

AD-A139 079

EVALUATION OF 'SORBOTHANE' CUSHIONING MATERIAL(U) AIR  
FORCE PACKAGING EVALUATION AGENCY WRIGHT-PATTERSON AFB  
OH MATERIALS ENGINEERING BRANCH M T WYDERSKI JAN 84  
DSTZT-83-R-12 F/G 11/9

1/1

UNCLASSIFIED

NL



END  
DATE  
FILMED  
4-84  
DTIC



MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

12

MARY T. WYDERSKI

Mechanical Engineer  
Materials Engineering Branch  
HQ AFLC/DSTZT

AUTOVON 787-7445  
COMMERCIAL (513) 257-7445

AD A 139079

EVALUATION OF "SORBOTHANE"  
CUSHIONING MATERIAL

HQ AFLC/DSTZ  
AIR FORCE PACKAGING EVALUATION AGENCY  
Wright-Patterson AFB OH 45433

DTIC  
ELECTE  
MAR 16 1984  
S D  
E

January 1984

DTIC FILE COPY

84 03 16 022

**NOTICE**

When government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related government procurement operation, the United States Government thereby incurs no responsibility whatsoever; and the fact that the government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto. This report is not to be used in whole or in part for advertising or sales purposes.

AFPEA PROJECT NO.: 82-P7-94  
 PROJECT TITLE: Evaluation of Sorbothane  
 PROJECT MONITOR: M. Wyderski

**ABSTRACT**

"Sorbothane", a high density polyurethane material with unusual displacement properties, is presently used extensively as a cushioning material for the human body in medical and sporting applications. This study was undertaken to consider possible packaging applications for this unique material in providing cushioning and shock isolation for Air Force equipment.

Various structural configurations of the material were subjected to dynamic cushioning evaluation. In addition the material was evaluated for its shear strength characteristics for possible use in shear mount type shock isolators.

Results of this evaluation indicate that dynamic cushioning characteristics of Sorbothane are only slightly better than some commonly used materials. The high density and cost of Sorbothane makes this material quite impractical as a cushioning material in comparison with the commonly used materials. The low shear strength of Sorbothane and its tendency to tear under shear loading makes it unsuitable for use in shock isolators.



Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
<b>A-1</b>	

PREPARED BY:  
*Mary T. Wyderski*  
 MARY T. WYDERSKI  
 Mechanical Engineer  
 AF Packaging Evaluation Agency

REVIEWED BY:  
*Matthew A. Venetos*  
 MATTHEW A. VENETOS  
 Chief, Materials Engineering Branch  
 AF Packaging Evaluation Agency

PUBLICATION DATE:

**04 JAN 1984**

APPROVED BY:  
*Jack E. Thompson*  
 JACK E. THOMPSON  
 Director, Air Force Packaging  
 Evaluation Agency

TABLE OF CONTENTS

	<u>PAGE</u>
Abstract . . . . .	i
Table of Contents . . . . .	ii
Introduction . . . . .	1
Material Description . . . . .	1
Test Specimens . . . . .	1
Test Equipment and Instrumentation . . . . .	2
Test Procedures	
Dynamic Cushioning Test . . . . .	2
Shear Strength Test . . . . .	2
Results/Discussion	
Dynamic Cushioning . . . . .	2
Shear Strength . . . . .	3
Conclusions . . . . .	3

FIGURES

Figure 1 - Dynamic Cushion Test Configurations . . . . .	4
Figure 2 - Shear Strength Test Apparatus . . . . .	5
Figure 3-6 - Peak "G" Acceleration vs Static Stress Curves . . . . .	6-9
Figure 7 - Shear Load vs Deflection . . . . .	10
Table I - Shear Strength Test Results for Specimen 1 . . . . .	11
Distribution List . . . . .	12
Report Documentation Page . . . . .	13

## INTRODUCTION

Sorbothane, a high density polyurethane material with unusual displacement properties, is currently being marketed as a cushioning material for the human body in medical and sporting applications. Possible applications of this material in Air Force packaging were investigated by this agency. Its use as a package cushioning material and as the main component in shock isolator devices was considered.

## MATERIAL DESCRIPTION

Sorbothane was developed in Great Britain by material scientists and orthopedic surgeons to reduce heel impact shock waves and, as a result, eliminate various neuroskeletal disorders such as arthritis, rheumatism, and backaches.

Sorbothane has a unique structure produced by the modification of a polyol-isocyanate reaction that results in a high percentage of short chain structures. The result is a material which has a dough-like texture though it retains permanent and measurable dimensions.

Some of the properties of Sorbothane are as follows:

1. Absorbs mechanical, acoustic and electromagnetic energy.
2. Sensitive to frequency of energy impulse.
3. Distorts readily, recovery slow-but controllable.
4. Compression set negligible.
5. Effective between  $-400^{\circ}\text{F}$  and  $+230^{\circ}\text{F}$ .
6. Fire retardant.
7. Liquid absorption, (including petroleum products), is negligible.
8. Inert to environmental attack.
9. Density normally  $83.6 \text{ lb/ft}^3$ , but can be foamed to reduce the density to about  $18.7 \text{ lb/ft}^3$ .

## TEST SPECIMENS

Four different configurations were subjected to dynamic cushioning evaluation. These configurations are illustrated in Figure 1. Configuration No. 1 was a solid block of Sorbothane with dimensions,  $2 \frac{3}{4}'' \times 2 \frac{3}{4}'' \times 2''$ . Configuration No's 2 and 3 each consisted of four small blocks of Sorbothane bonded to the corners of an  $8'' \times 8''$  piece of solid fiberboard. Configuration No. 4 consisted of polyurethane foam strips bonded to Sorbothane strips.

Shear strength tests were conducted on specimens measuring  $1 \frac{7}{16}'' \times \frac{7}{8}'' \times 1''$  and  $5'' \times \frac{13}{16}'' \times 1''$ . The shear stress was applied across the one-inch thickness of the specimens.

## TEST EQUIPMENT AND INSTRUMENTATION

The following test equipment and instrumentation were used to conduct this study:

1. Hardigg Cushion Tester, Hardigg Industries Inc., Model No. 3.
2. Oscilloscope, 4 channel storage, Tektronix Model 564-B.
3. Accelerometer, Statham Model A5-100-350.
4. Amplifier, Sensotec Model RM-6.
5. Energy Computer, EC700, GHI Systems, Serial No. 90809.

## TEST PROCEDURES

### Dynamic Cushioning Test

The various configurations (see Figure 1) were subjected to dynamic cushioning evaluation in accordance with ASTM Standard D1596, "Shock Absorbing Characteristics of Package Cushioning Materials". Drop heights of 12", 18" and 24" were used. Static stress loads were varied at each drop height. Five drops were made on each sample at each static stress load with allowance of one minute between drops to allow for specimen recovery. The last four peak acceleration values recorded for each set of five drops were averaged and the average values were plotted in the form of peak acceleration (G's) vs static stress curves.

### Shear Strength Test

Two samples were tested for shear strength. Each sample was bonded between two metal plates, as shown in Figure 2. One plate was suspended from a fixed support while the other plate was loaded by attaching a can containing weights to its lower edge. Deflection was measured from the top edge of the loaded plate with reference to the adjacent fixed plate at 24 hour intervals; additional weight increments were added after each 24 hour interval.

## RESULTS/DISCUSSION

### Dynamic Cushioning

Results are shown in Figures 3-7. Figure 3 indicates that Sorbothane has cushioning properties similar to polyethylene foam of 6 lb/ft<sup>3</sup> for static stress loads less than 4.0 psi. At static stress loads greater than 7.9 psi, Sorbothane is slightly better than polyethylene of 9.0 lb/ft<sup>3</sup> density.

Figure 4 indicates that Configuration 1 provided the most favorable dynamic cushioning properties. The effective bearing area of the Sorbothane material of Configurations 2, 3 and 4 was used to determine the static stress loads in this figure. The Sorbothane in Configurations 2, 3 and 4 was arranged to provide a greater effective loading base area in an attempt to eliminate the buckling effect noted during the evaluation of Configuration 1. However,

all of these configurations still gave evidence of buckling.

Compared with polyethylene, 4 lb/ft<sup>3</sup> density, the combination sample of alternating polyurethane foam and Sorbothane strips (Configuration 4), indicated somewhat similar, though more favorable cushioning characteristics (see Figures 5 and 6).


#### Shear Strength

Results for shear strength test specimen #1 are shown in Table I and Figure 7. The test specimen tore at four locations on the top surface after application of 12.8 lbs for a period of 24 hours. All four tears were located within 1/4" from the fixed plate. These tears were 3/8" - 3/4" in length and approximately 1/8" in depth. After the load was increased to 14.9 lbs for an additional 8 hours, three of the tears increased to 3/4" in length and the test was terminated. Specimen No. 2, after being subjected to 2.3 lbs for 24 hours, tore along the entire length of the top surface of the sample within 1/32" of the fixed plate.


#### CONCLUSIONS

Based on the results of this evaluation, it was concluded that it would not be feasible to consider Sorbothane for use as a cushioning material in package designs or as a shock isolator. Although the dynamic cushioning characteristics of Sorbothane were slightly better than comparable commonly used cushioning materials, Sorbothane is significantly higher in both cost and density. The tearing of this material under light shear loads precludes its use in shear mounts.




CONFIGURATION 1.

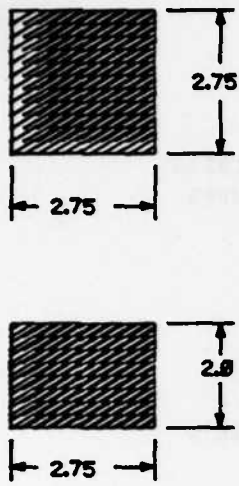

CONFIGURATION 2.

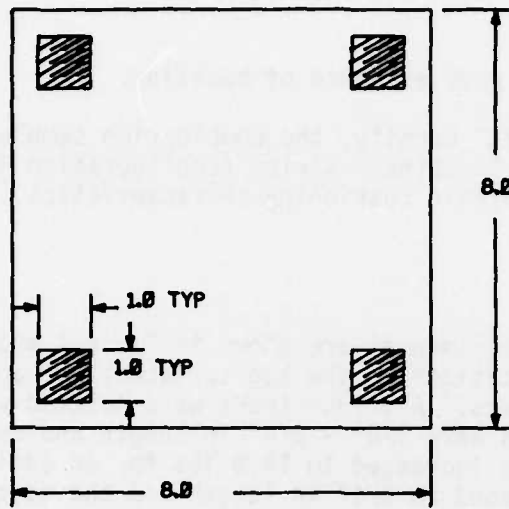

CONFIGURATION 3.

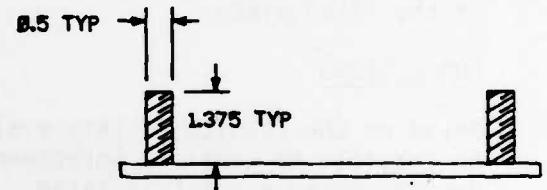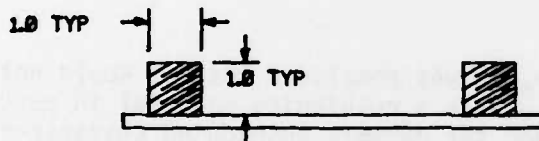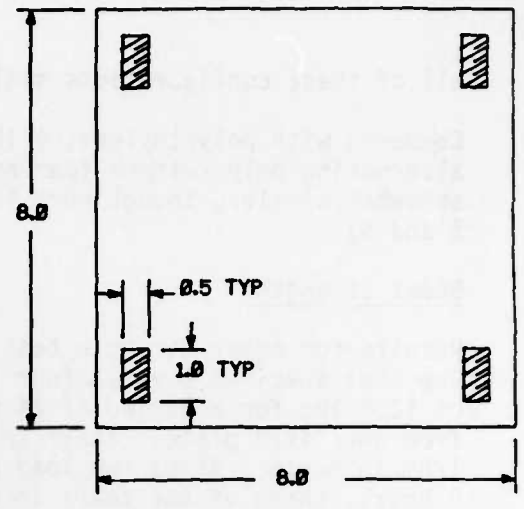

CONFIGURATION 4.


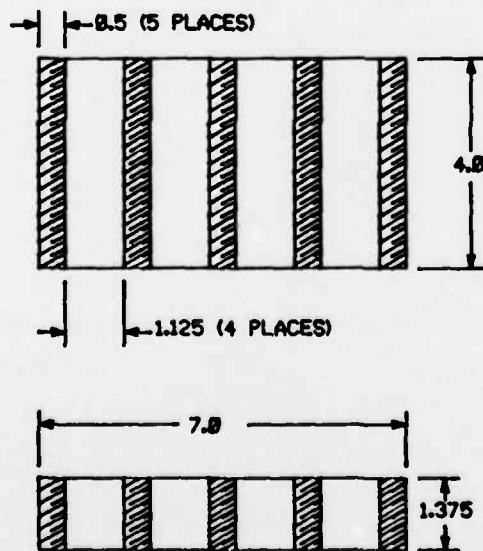



FIGURE 1 - DYNAMIC CUSHION TEST CONFIGURATIONS.

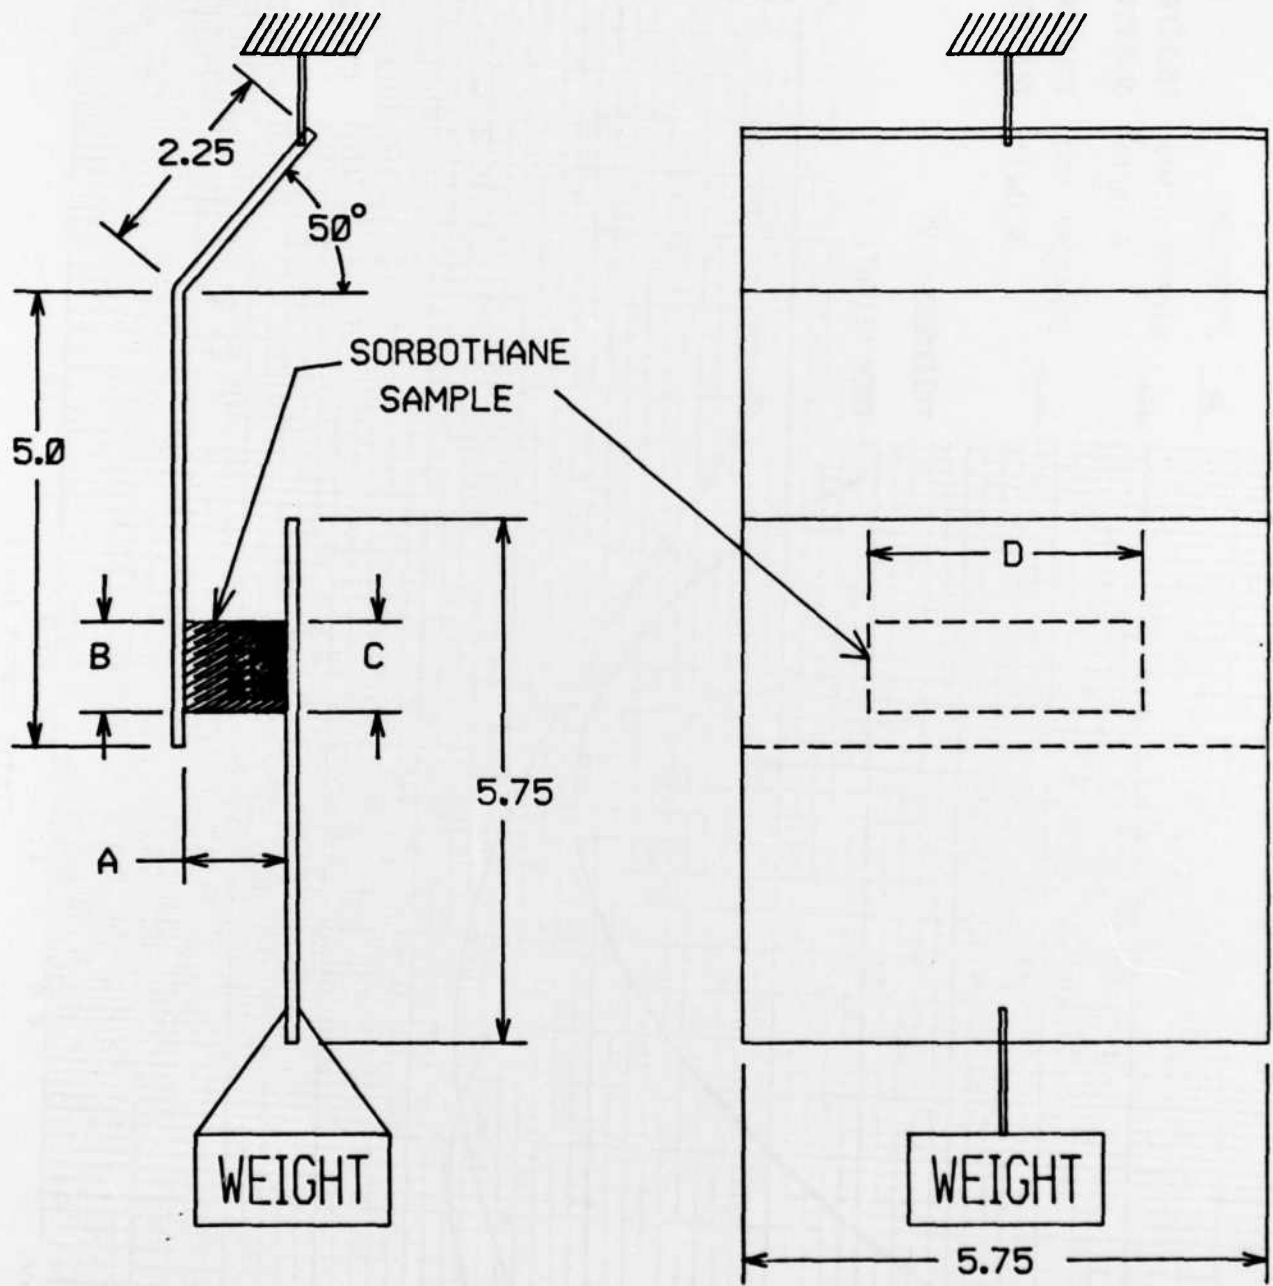

SAMPLE 1.    A= 1.125  
                   B= 1.0  
                   C= 0.75  
                   D=5.0

SAMPLE 2.    A=1.0  
                   B= 1.8125  
                   C= 0.8125  
                   D= 1.4375


FIGURE 2. SHEAR STRENGTH TEST APPARATUS.

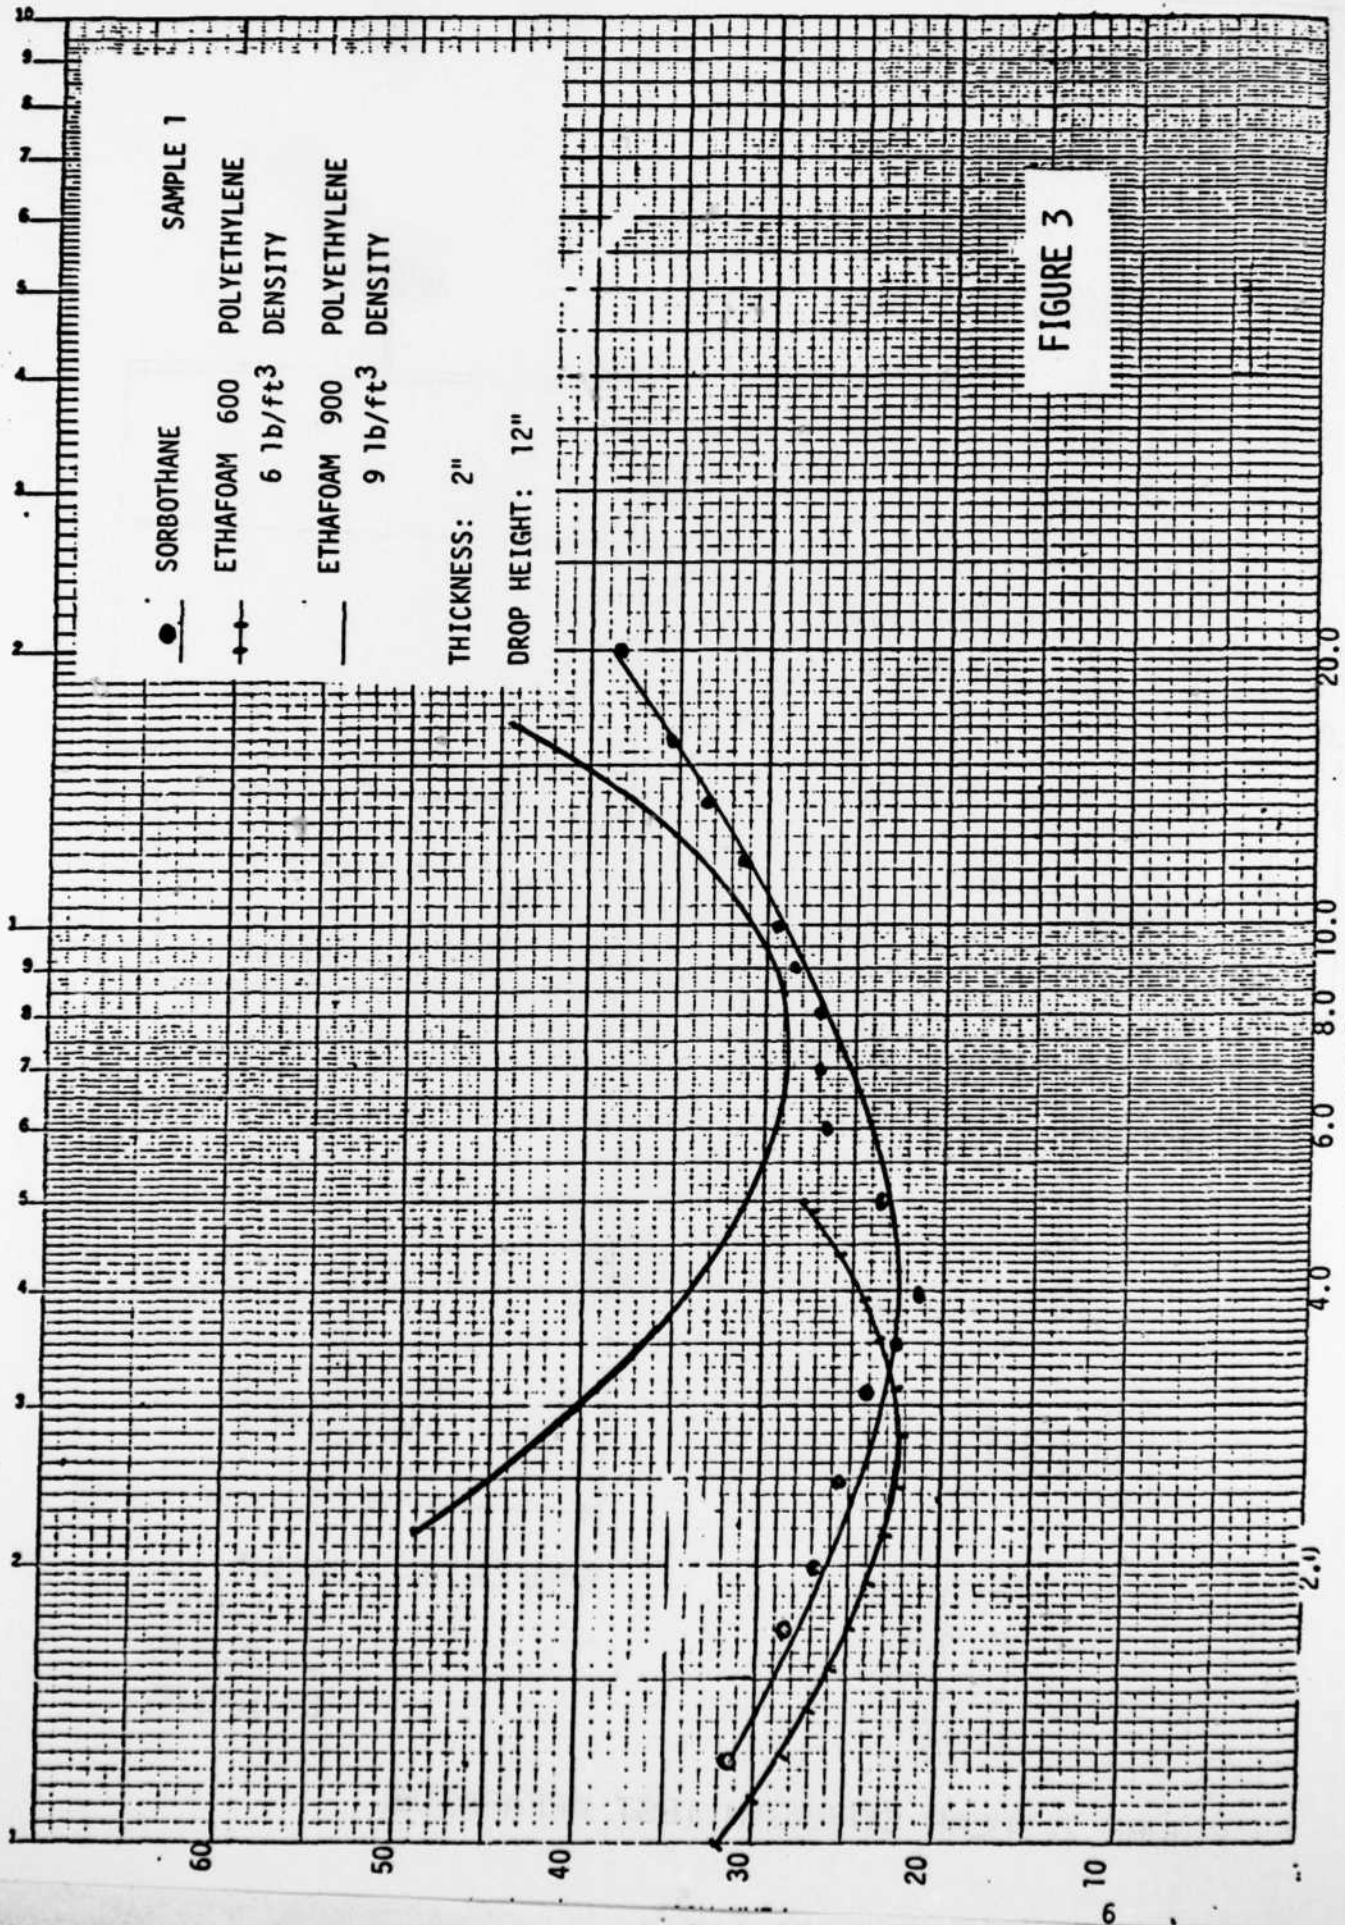

STATIC STRESS (psi)

TRANSMISSION PHOTOGRAPH OF POLYMER FILM  
PREPARED BY DR. G. V. SCHULZ, JR.

SEE IN USE

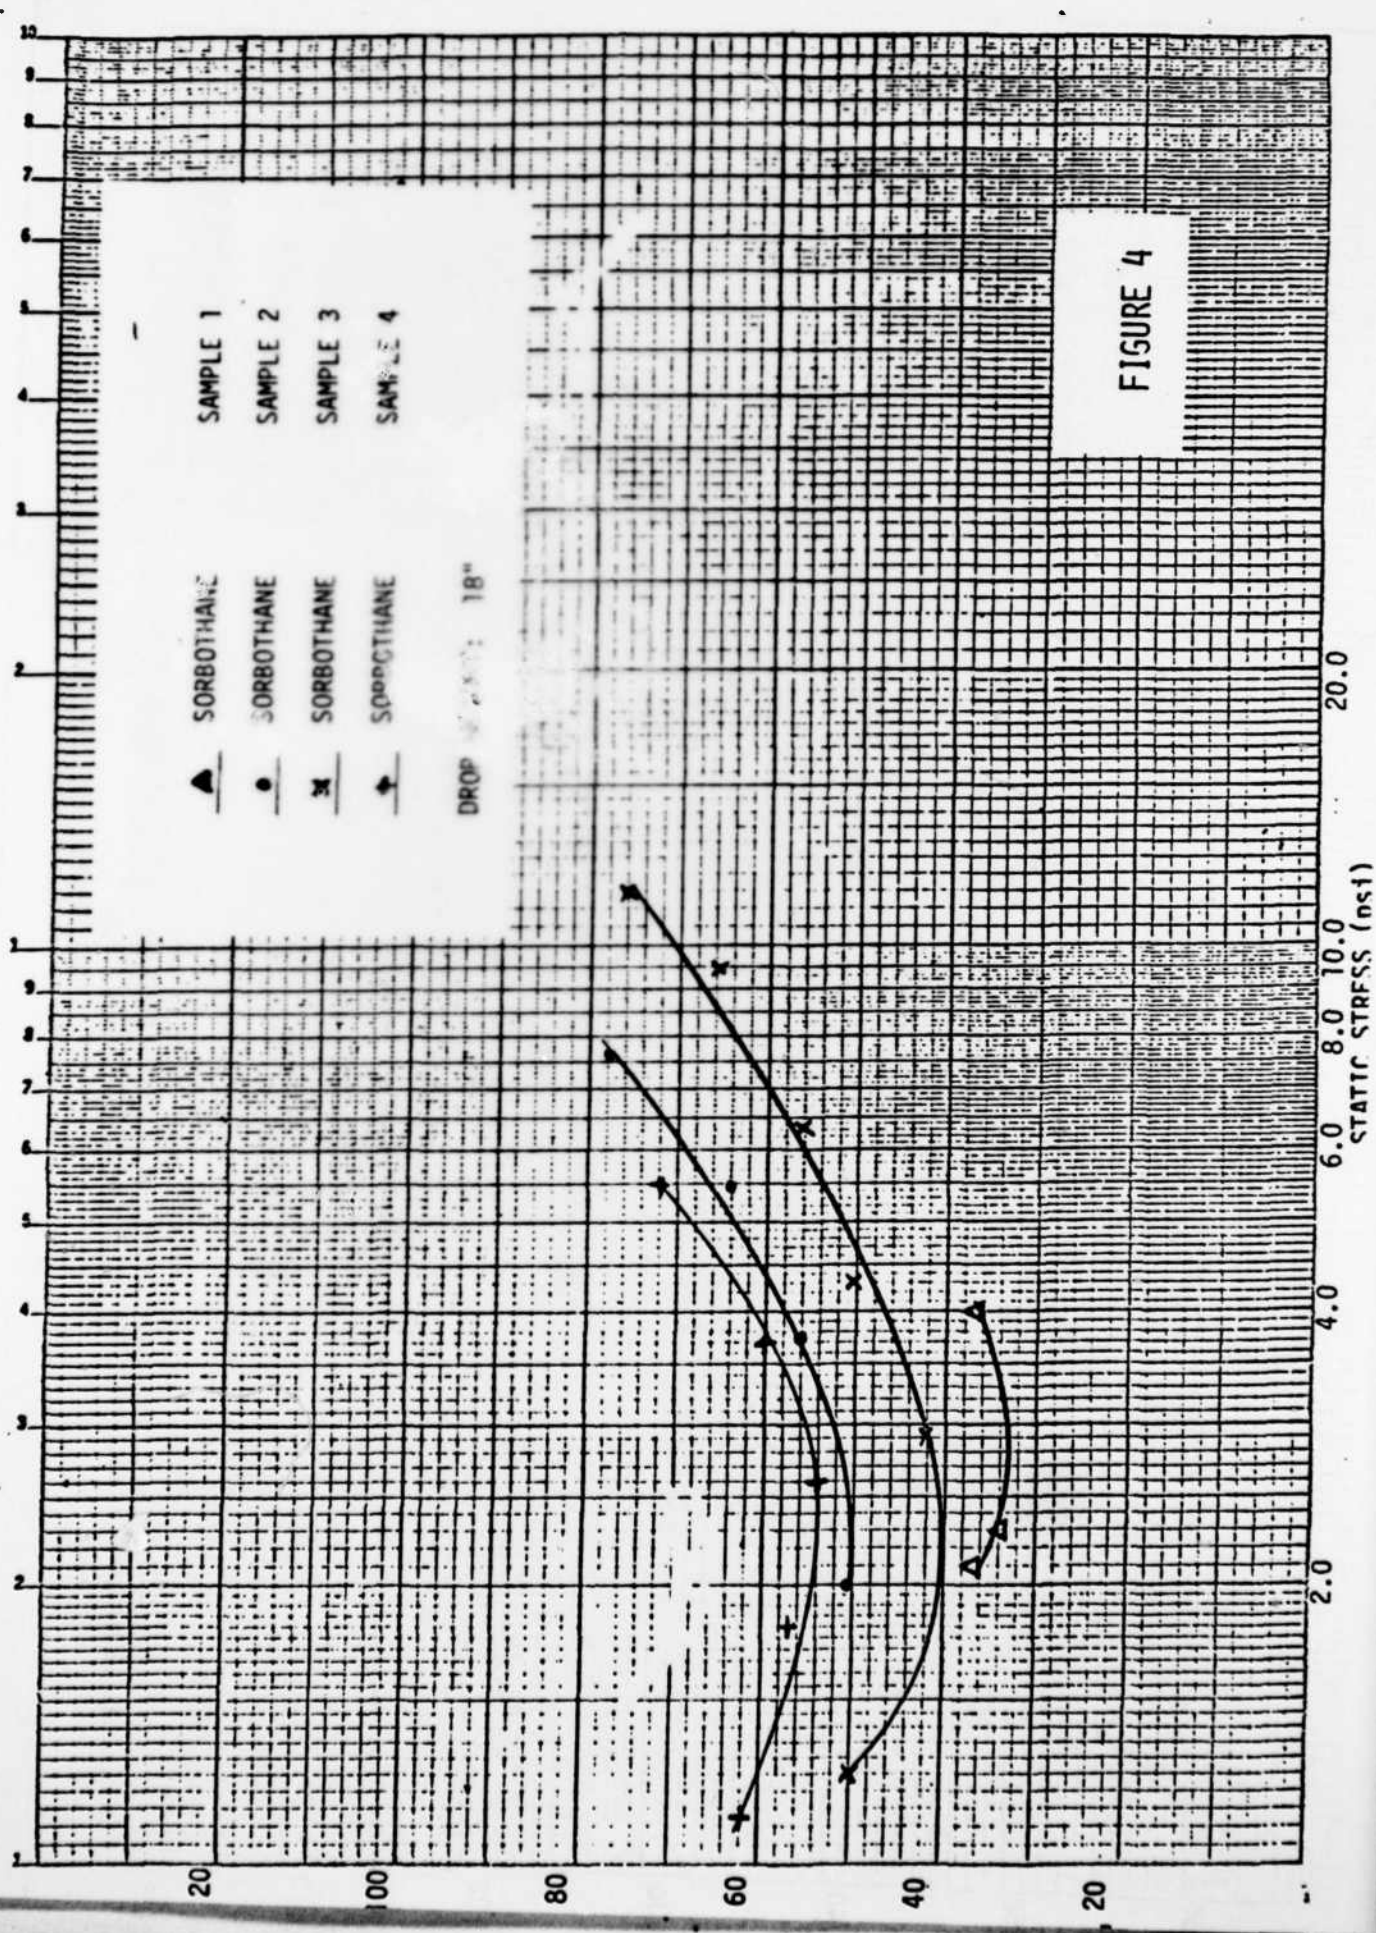

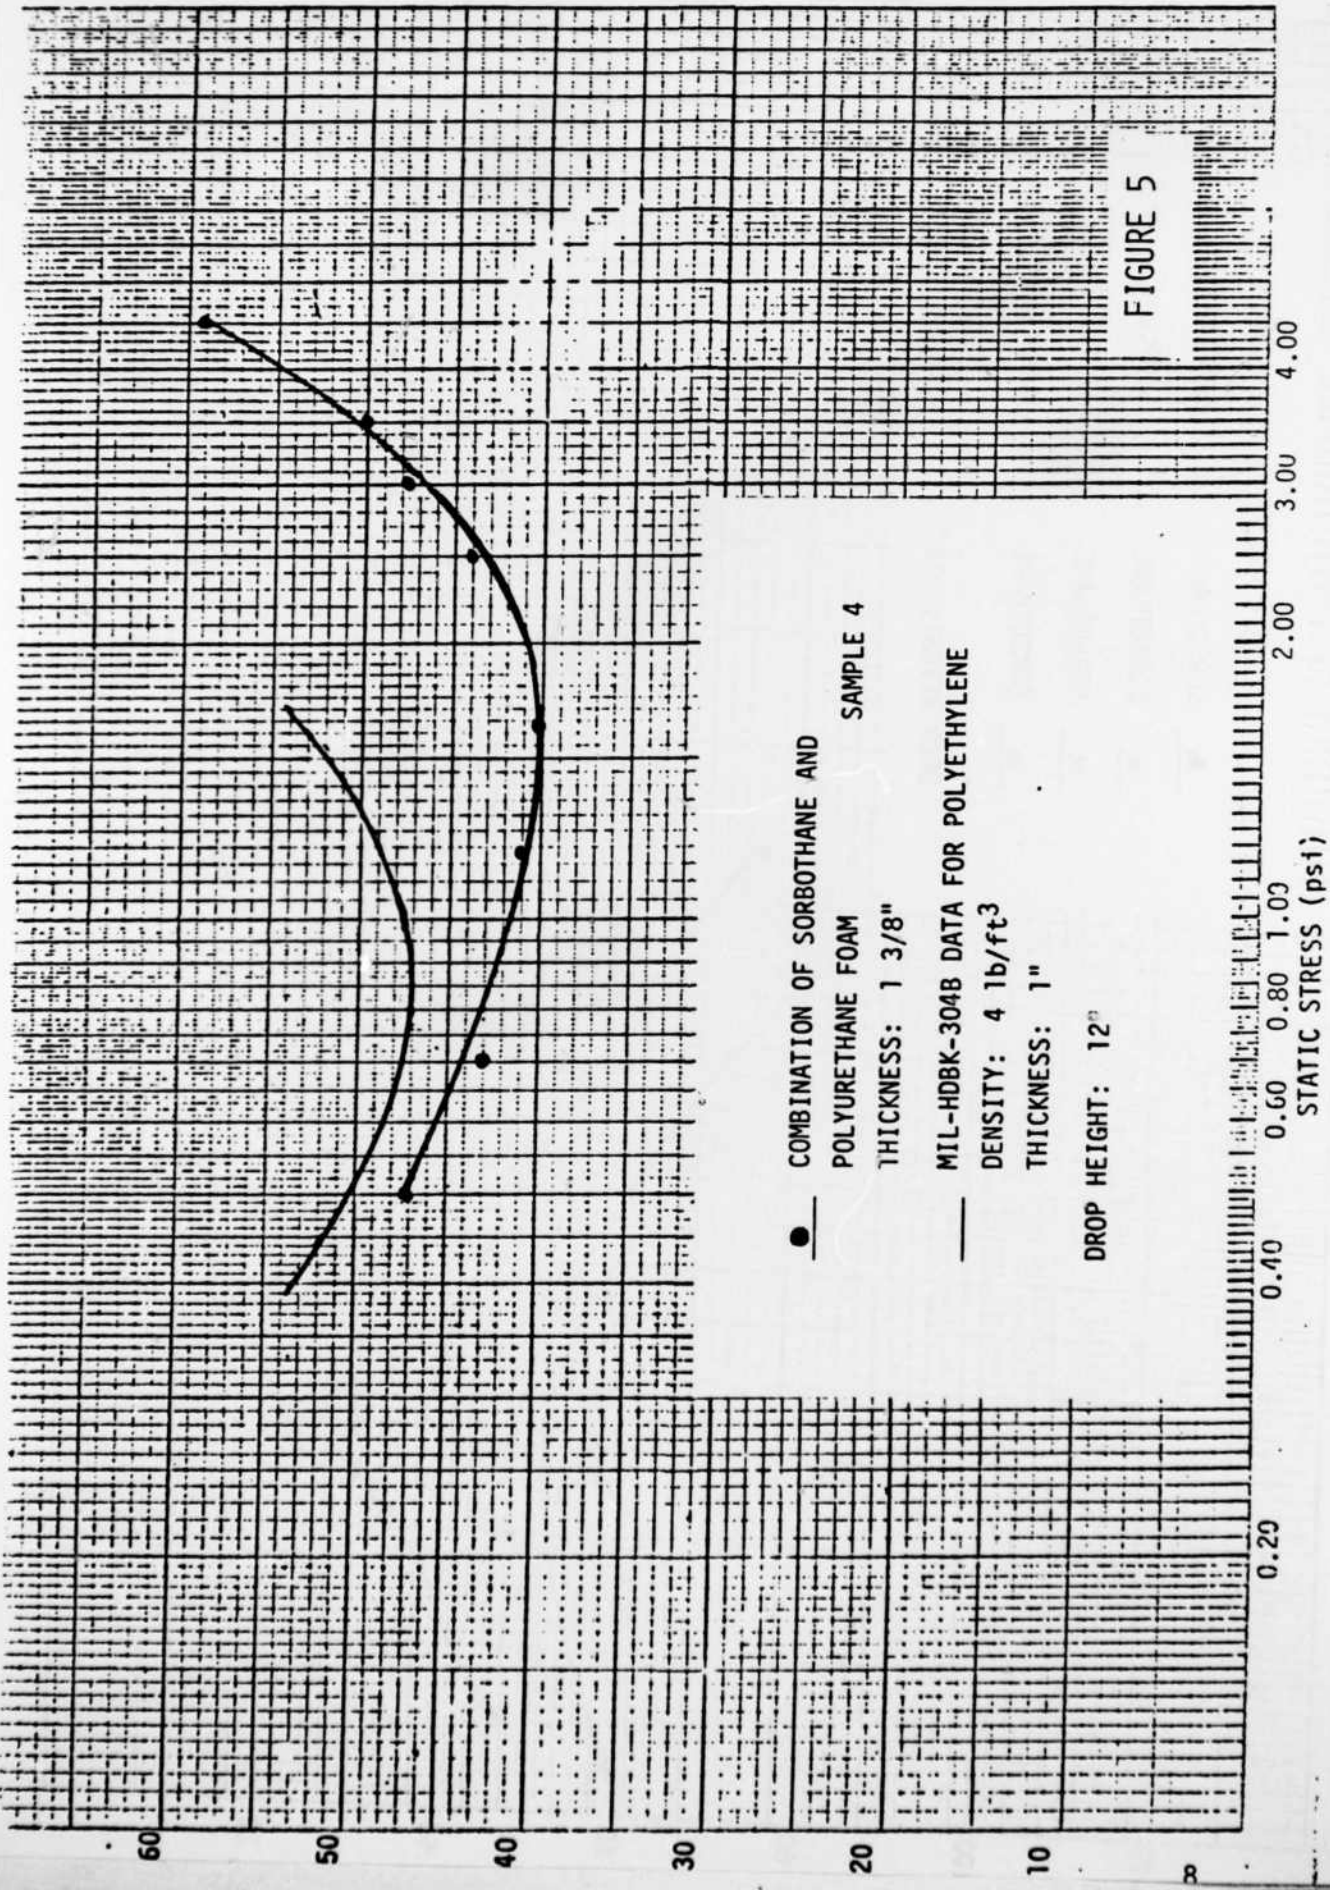


FIGURE 5

REVISION: 1 BY 10 017/118

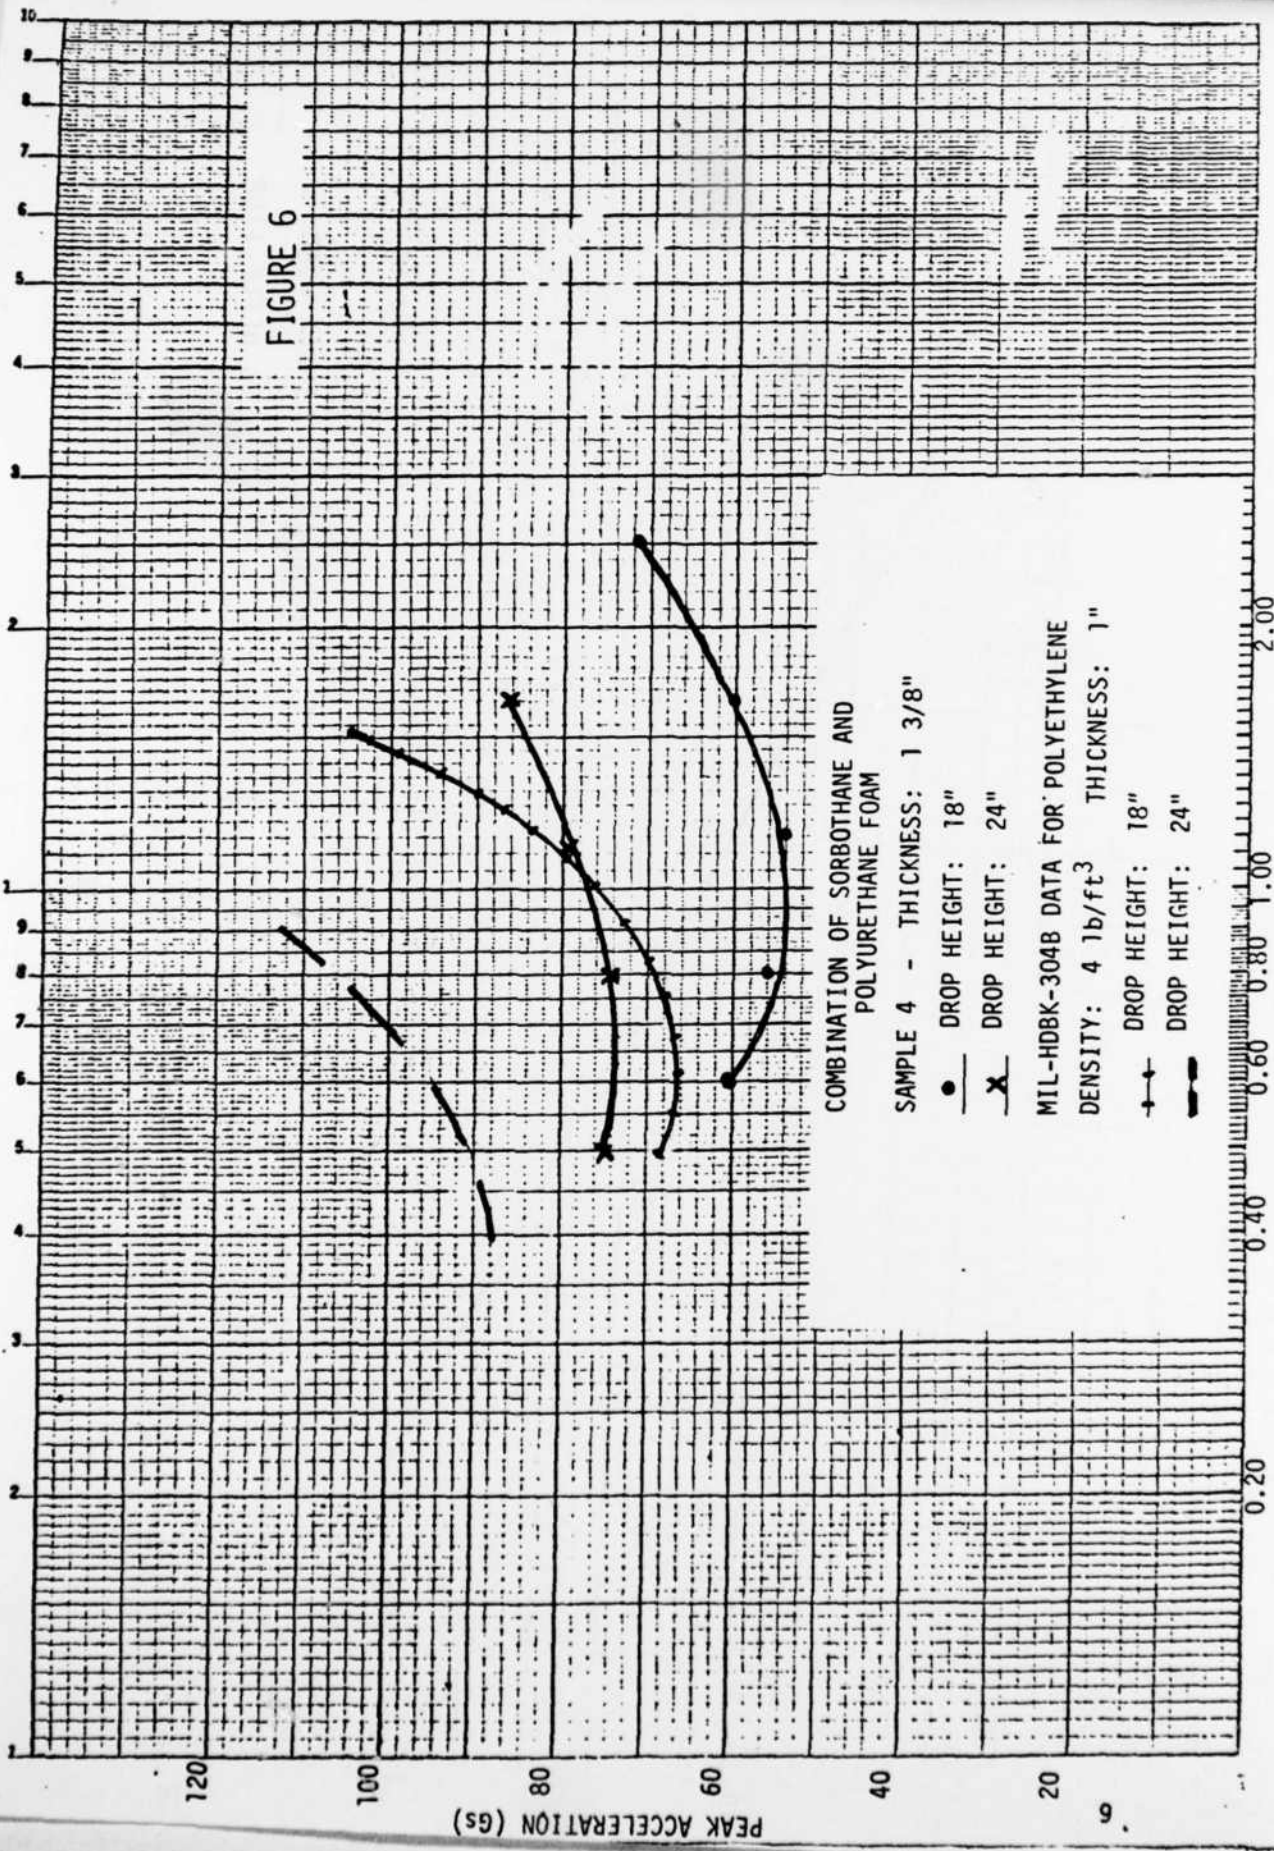


FIGURE 6

COMBINATION OF SORBOTHANE AND POLYURETHANE FOAM

SAMPLE 4 - THICKNESS: 1 3/8"

● DROP HEIGHT: 18"

✕ DROP HEIGHT: 24"

MIL-HDBK-304B DATA FOR POLYETHYLENE

DENSITY: 4 lb/ft<sup>3</sup> THICKNESS: 1"

—+— DROP HEIGHT: 18"

—+— DROP HEIGHT: 24"

STATIC STRESS (psi)

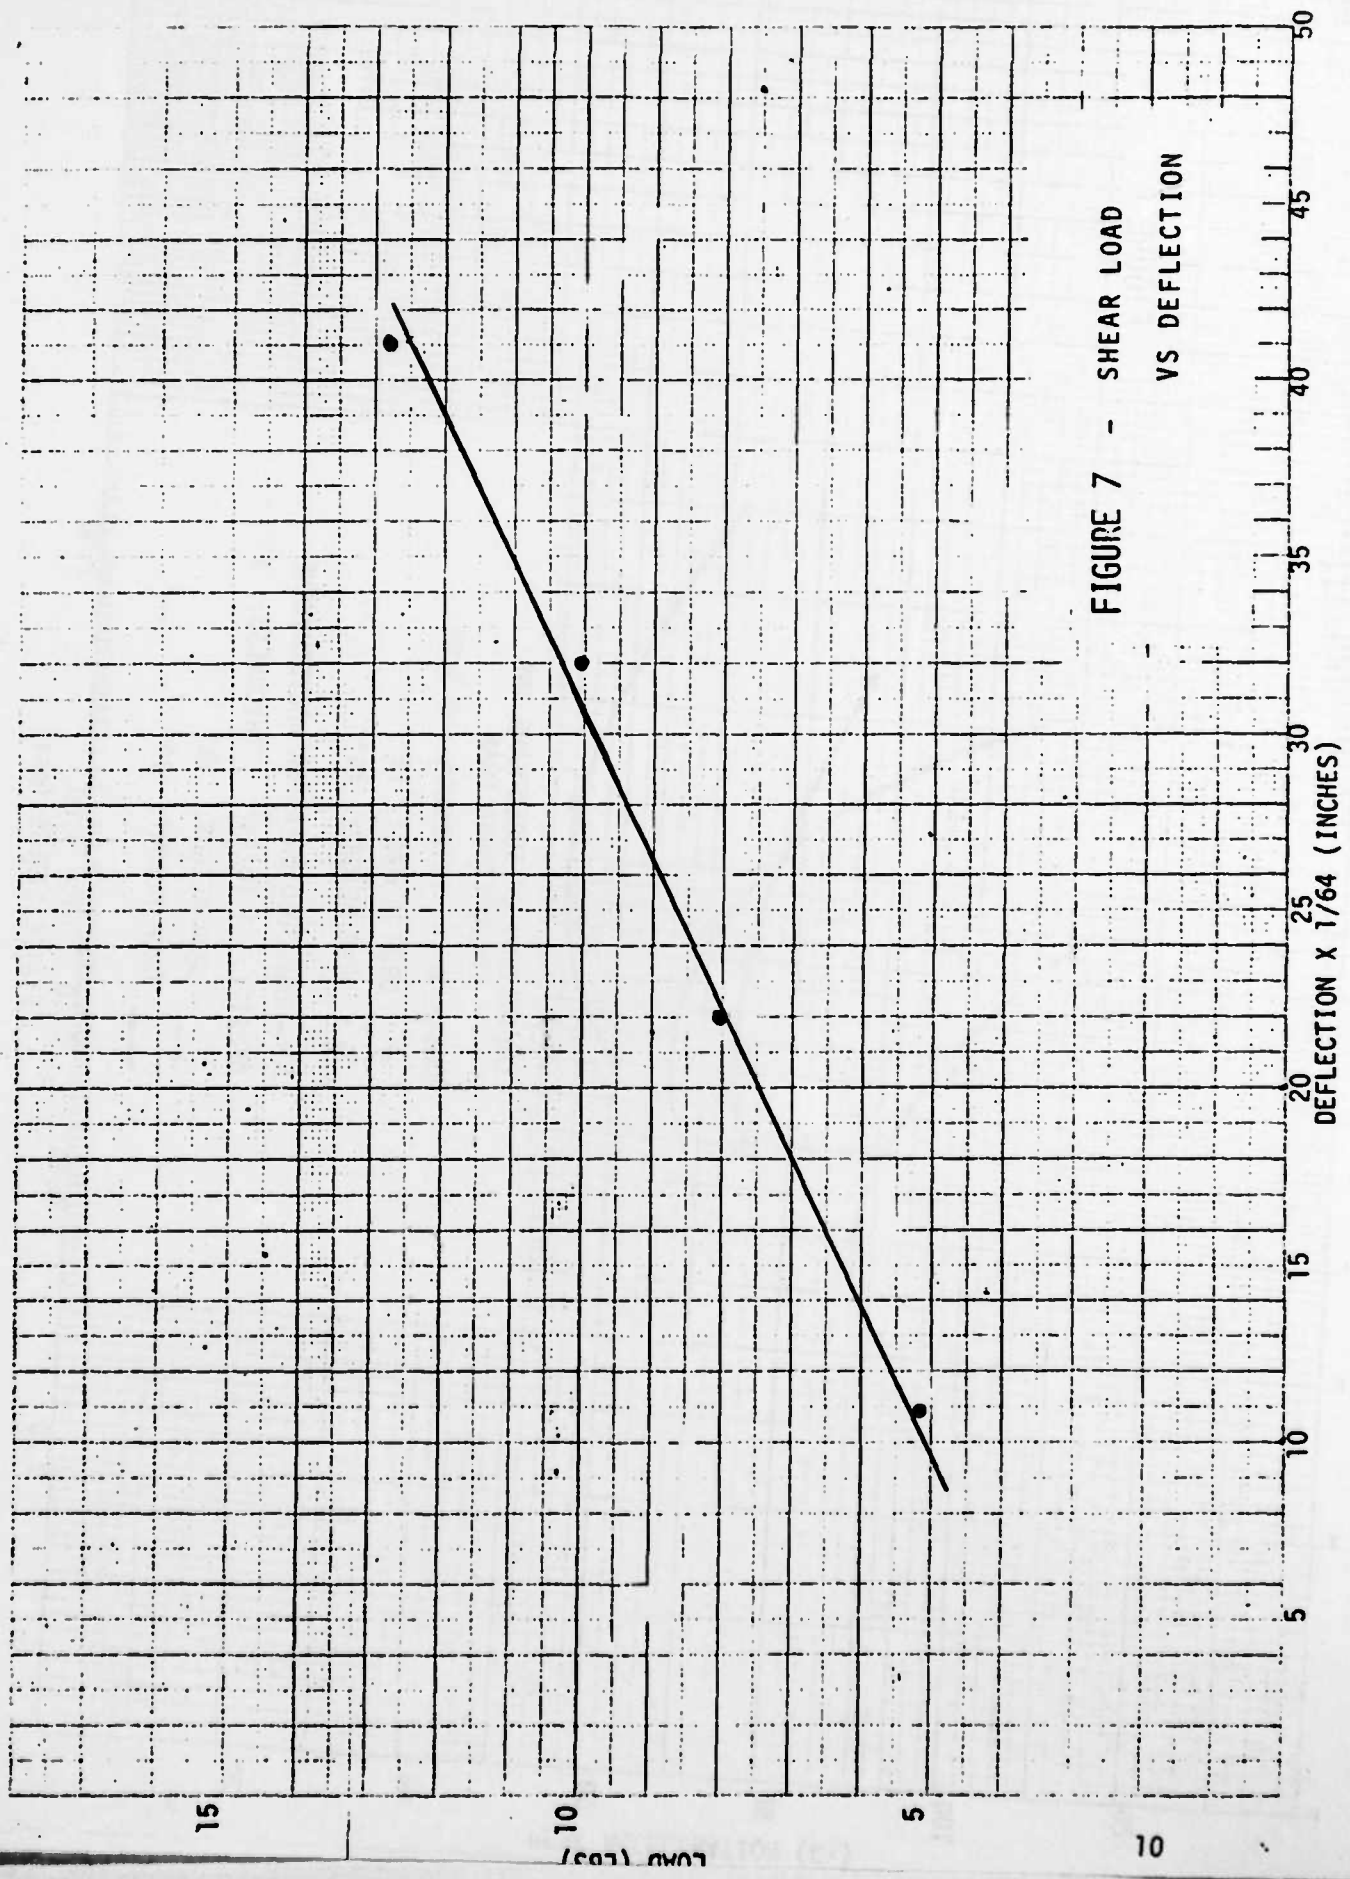


FIGURE 7 - SHEAR LOAD VS DEFLECTION

3  
 150  
 100  
 50

TABLE I - SHEAR STRENGTH TEST RESULTS FOR SPECIMEN 1

TOTAL LOAD APPLIED (LBS)	TIME PERIOD OF LOAD APPLICATION (HOURS)	INCREMENTAL DEFLECTION OF LOADED PLATE (INCHES)	TOTAL DEFLECTION OF LOADED PLATE (INCHES)
5.1	21.9	6/32"	6/32"
7.9	24.4	5/32"	11/32"
9.9	23.85	5/32"	16/32"
12.8	24.17	9/65"	41/64"

DISTRIBUTION LIST

ADTC/YXC Eglin AFB FL 32542	1	HQ DLA-OWO Cameron Station Alexandria VA 22314	1
ASD/AWL WPAFB OH 45433	1	HQ USAF/LETT Wash DC 20330	1
ASO/TEP-A-4030 700 Robbins Avenue Philadelphia PA 19111	1	NAVSUPSYSCMD Attn: SUP-0321A Wash DC 20376	5
DARCOM Attn: SDSTO-T Tobyhanna PA 18466	1	OC-ALC/DSP Tinker AFB OK 73145	1
DLSIE USA Logistics Management Center Attn: DRXMC-D Ft Lee VA 23801	1	OO-ALC/DSP Hill AFB UT 84056	1
DTIC/TSR Cameron Station Alexandria VA 22314	12	SA-ALC/DSP Kelly AFB TX 78241	1
GSA, Office of Engrg Mgmt Packaging Division Wash DC 20406	1	SM-ALC/DSP McClellan AFB CA 95652	1
HQ AFLC/DST WPAFB OH 45433	1	US Army Armament Research & Development Command Attn: DRDAR-TST-S Dover NJ 07801	1
HQ AFLC/DSTP WPAFB OH 45433	1	US Army Natick Labs Attn: DRDNA-EPS Natick MA 01760	1
HQ AFLC/DSTZT LIBRARY WPAFB OH 45433	20	WR-ALC/DSP Robins AFB GA 31098	1

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

## REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION <b>UNCLASSIFIED</b>		1b. RESTRICTIVE MARKINGS N/A	
2a. SECURITY CLASSIFICATION AUTHORITY N/A		3. DISTRIBUTION/AVAILABILITY OF REPORT APPROVED FOR PUBLIC RELEASE DISTRIBUTION UNLIMITED	
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE N/A		4. PERFORMING ORGANIZATION REPORT NUMBER(S)  DSTZT REPORT NO. 83-R-12	
5. MONITORING ORGANIZATION REPORT NUMBER(S)  N/A		6a. NAME OF PERFORMING ORGANIZATION Air Force Packaging Evaluation Agency	
6b. OFFICE SYMBOL (If applicable) HQ AFLC/DSTZT		7a. NAME OF MONITORING ORGANIZATION  N/A	
6c. ADDRESS (City, State and ZIP Code)  Wright-Patterson AFB OH 45433		7b. ADDRESS (City, State and ZIP Code)  N/A	
8a. NAME OF FUNDING/SPONSORING ORGANIZATION N/A		8b. OFFICE SYMBOL (If applicable) N/A	
9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER  N/A		10. SOURCE OF FUNDING NOS.	
8c. ADDRESS (City, State and ZIP Code)  N/A		PROGRAM ELEMENT NO.	PROJECT NO.
11. TITLE (Include Security Classification) Evaluation of "Sorbothane" Cushioning Material		TASK NO.	WORK UNIT NO.
12. PERSONAL AUTHOR(S) Mary T. Wyderski		N/A	
13a. TYPE OF REPORT FINAL REPORT	13b. TIME COVERED FROM Dec 82 TO Jan 84	14. DATE OF REPORT (Yr., Mo., Day) January 1984	15. PAGE COUNT 16
16. SUPPLEMENTARY NOTATION  N/A			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB. GR.	
13	04	N/A	
19. ABSTRACT (Continue on reverse if necessary and identify by block number)		Sorbothane Conformal Cushioning Dynamic Cushioning Polyurethane	
"Sorbothane", a high density polyurethane material with unusual displacement properties, is presently used extensively as a cushioning material for the human body in medical and sporting applications. This study was undertaken to consider possible packaging applications for this unique material in providing cushioning and shock isolation for Air Force equipment. Various structural configurations of the material were subjected to dynamic cushioning evaluation. In addition the material was evaluated for its shear strength characteristics for possible use in shear mount type shock isolators. Results of this evaluation indicate that dynamic cushioning characteristics of Sorbothane are only slightly better than some commonly used materials. The high density and cost of Sorbothane makes this material quite impractical as a cushioning material in comparison with the commonly used materials. The low shear strength of Sorbothane and its tendency to tear under shear loading makes it unsuitable for use in shock isolators.			
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS <input type="checkbox"/>		21. ABSTRACT SECURITY CLASSIFICATION  UNCLASSIFIED	
22a. NAME OF RESPONSIBLE INDIVIDUAL  MARY T. WYDERSKI		22b. TELEPHONE NUMBER (Include Area Code) (513)257-4519	22c. OFFICE SYMBOL  HQ AFLC/DSTZT

**DATE**  
**FILME**