

7

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1 REPORT NUMBER 5	7 GOVT ACCESSION NO	3 RECIPIENT'S CATALOG NUMBER
2 TITLE and Subtitle Angle-Resolved Photoemission Study of AuGa ₂ and AuIn ₂ Intermetallic Compounds		5 TYPE OF REPORT & PERIOD COVERED Technical Report
		6 PERFORMING ORG REPORT NUMBER
4 AUTHOR Jeffrey G. Nelson, W.J. Giamac, Sehun Kim, Jeffrey R. Lance and R. Stanley Williams		8 CONTRACT OR GRANT NUMBER(s) N00014-83-K-0612
PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry & Biochemistry UCLA - Los Angeles, CA 90024		10 PROGRAM ELEMENT PROJECT TASK AREA & WORK UNIT NUMBERS
CONTROLLING OFFICE NAME AND ADDRESS Chemistry Program Office Office of Naval Research, Arlington, VA 22217		12 REPORT DATE December 1984
11 MONITORING AGENCY NAME & ADDRESS if different from Controlling Office:		13 NUMBER OF PAGES
		15 SECURITY CLASS (of this report) UNCLASSIFIED
DISTRIBUTION STATEMENT of this Report Approved for public release; distribution unlimited		15a DECLASSIFICATION DOWNGRADING SCHEDULE

AD-A150 000

DISTRIBUTION STATEMENT of the abstract entered in Block 20 if different from Report

DTIC
COLLECTED
1 FEB 03 1985

18 SUPPLEMENTARY NOTES
To be published in Physical Review B

Gamma

19 KEY WORDS (Continue on reverse side if necessary and identify by block number)
Synchrotron radiation - angle-resolved photoemission - valence band structure
- d-bands - surface state.

In 1/a

20 ABSTRACT (Continue on reverse side if necessary and identify by block number)
The (001) surfaces of AuGa₂ and AuIn₂ intermetallic compounds were studied using synchrotron radiation excited angle-resolved photoemission. Spectra collected for photoelectron emission normal to the sample surfaces were used to map the E versus k dispersion relation of both compounds along the $\bar{\Gamma}$ symmetry line of the bulk Brillouin Zone. The results show that the Au 5d bands of each compound are relatively flat, but the splittings of the bands at $\bar{\Gamma}$ are nearly the same as for elemental Au. A surface state is also observed on each surface in a band-gap region about 6 eV below the Fermi levels of the 2 compounds.

DTIC COPY

Information for use requests include:

DISCLAIMER NOTICE

**THIS DOCUMENT IS BEST QUALITY
PRACTICABLE. THE COPY FURNISHED
TO DTIC CONTAINED A SIGNIFICANT
NUMBER OF PAGES WHICH DO NOT
REPRODUCE LEGIBLY.**

**Angle-Resolved Photoemission Study
of AuGa₂ and AuIn₂ Intermetallic Compounds**

**Jeffrey G. Nelson, W.J. Gignac, Sehun Kim,
Jeffrey R. Lince and E. Stanley Williams**

**Department of Chemistry and Biochemistry
University of California, Los Angeles
Los Angeles, California 90024**

Abstract

The (001) surfaces of AuGa₂ and AuIn₂ intermetallic compounds were studied using synchrotron radiation excited angle-resolved photoemission. Spectra collected for photoelectron emission normal to the sample surfaces were used to map the E versus $\frac{1}{2}$ dispersion relation of both compounds along the Δ symmetry line of the bulk Brillouin Zone. The results show that the Au 5d bands of each compound are relatively flat, but the splittings of the bands at F are nearly the same as for elemental Au. A surface state is also observed on each surface in a band gap region about 6 eV below the Fermi levels of the two compounds.

I. Introduction

Au, AuGa₂ and AuIn₂ form an interesting series of metals for the study of the Au 5d orbitals in solids. In elemental Au, the atoms reside on a face-centered cubic (fcc) lattice with a nearest-neighbor distance of 2.88 Å. AuGa₂ and AuIn₂ have the fluorite structure, in which the Au atoms form an fcc sublattice where each Au atom is at the center of a cube with eight group III (Ga or In) atoms situated at the corners. In this arrangement, the Au-Au nearest-neighbor distances are 4.29 Å and 4.60 Å for AuGa₂ and AuIn₂, respectively. The strength of the interaction between the 5d orbitals on neighboring Au atoms in this group should decrease dramatically with increasing atomic separation and should be evident as a narrowing in the d-band structure of these metals. Examining the energy bands of these materials at the Γ point of the Brillouin Zone (BZ), where each band reduces to a single type of atomic d character, will provide interesting information about the Au d - d interactions as a function of primarily interatomic distance.

Au is an extremely well-studied material, but most previous investigations of the electronic structure of the Au(group III)₂ intermetallic compounds have been limited to optical reflectivity measurements,¹ Fermi surface determinations,^{2,3} and total valence band density-of-state measurements.⁴⁻⁶ The results of van Attekum, et al.,⁶ show that the total Au 5d-band width, as measured using x-ray photoelectron spectroscopy (XPS) of polycrystalline samples, decreases in the series Au, AuGa₂, and AuIn₂. More recently, the surface net and electronic structure of the AuGa₂ (001) single-crystal surface have been studied using

low-energy electron diffraction (LEED), Auger electron spectroscopy (AES) and electron-energy loss spectroscopy (EELS),⁷ in preparation for more detailed investigations of the electronic band structure.

Angle-resolved photoelectron spectroscopy (ARPES) has proved to be an effective technique for studying the electronic structure of single-crystal materials by providing information about the E versus \underline{k} dispersion relation along specific directions in the BZ.⁸⁻¹⁰ This technique is well suited to measure the binding energies of the Au 5d-levels at various points in the BZ, which is necessary to study the Au 5d-5d interactions in the Au, AuGa₂, AuIn₂ series. This type of detailed electronic structure measurement has not previously been applied to these intermetallic compounds.

Switendick and Narath¹¹ have calculated non-relativistic APW band structures for AuAl₂, AuGa₂, and AuIn₂. These calculations show a marked narrowing in the d-bands of AuIn₂ compared to AuGa₂. Both the splitting of the bands at Γ and the band dispersion as \underline{k} varied outward to the BZ boundaries were much smaller for AuIn₂. However, the total width of the calculated d-bands was much smaller than indicated by the XPS valence band spectra⁶ of both compounds. Since the calculations neglected spin-orbit splitting, which should be large in Au 5d orbitals, this last observation is perhaps not surprising.

In order to assist in understanding the d-band structure of AuGa₂ and AuIn₂, a mixed basis band structure interpolation scheme including spin-orbit splitting was developed.¹² The interpolation scheme was first fit to the APW calculations, and then the parameters were adjusted to improve the agreement between the ARPES and the calculated bands at Γ . In

this way, semi-empirical band structures for both AuGa₂ and AuIn₂ were constructed, which enabled the symmetries of valence bands to be determined, and helped with the interpretation of all the ARPES spectra.

The focus of this paper will be on mapping the band structure of AuGa₂ and AuIn₂ along Δ using normal-emission ARPES from (001) surfaces of single crystals. From the results of the experimental bulk band structures at Γ , the "crystal field" (Δ) and the spin-orbit (ξ) parameters for the Au, AuGa₂ and AuIn₂ series were calculated in order to look at the Au 5d-5d interactions as a function of interatomic distance. A surface state was also observed on both surfaces inside a band gap region of the d-bands along the Δ symmetry axis of the BZ. Sec. II will describe the experimental procedure followed in this work, while Sec. III presents the results of the ARPES experiments on AuGa₂ and AuIn₂. A discussion of the findings of this work and their relationship to previous studies appears in Sec. IV.

II. Experimental Procedure

The experiments were performed on beam line I-2 (the 8° port) at the Stanford Synchrotron Radiation Laboratory (SSRL). All ARPES measurements were made in an ultra-high vacuum analysis chamber provided by SSRL with a base pressure of 6×10^{-10} torr. The chamber was equipped with a single axis sample manipulator, LEED optics, and a Vacuum Generators, Ltd. (VG) ADES 400 angle-resolving photoelectron spectrometer that had an acceptance cone half angle of $\sim 3^\circ$. Both samples were mounted such that the plane of incidence of the photon beam contained the polarization vector of the radiation (p-polarized) and the [110] axis of the crystals. Both normal and off-normal emission spectra were collected with the photon beam 45° from the [001] axis of the samples. A single spectrum required approximately seven minutes to collect in order to insure that there were a minimum of three thousand counts in the strongest feature of each spectrum. The storage ring (SPEAR) was typically operating with a beam energy of 3.0 GeV and a current of between 30 and 60 mA. Photon energies in the range of 14 to 32 eV were used, and the total analyzer plus monochromator energy resolution was better than 0.2 eV in all cases. All of the ARPES data were collected with the sample at room temperature.

The Energy Distribution Curves (EDC) were collected as a function of photoelectron kinetic energy. In order to determine a reference binding energy for all the spectra, a Fermi Level (E_F) was assigned to spectra that were the sums of all ARPES spectra collected at each photon energy, in order to include initial states from a reasonably large portion of the BZ. This was accomplished by establishing a baseline for each summed spectrum.

and then defining E_F to be the energy where the EDC crossed a line that was half the distance from the baseline to a second line that was fit to the flat s-p plateau of that EDC.

The procedure for the preparation of the AuGa₂ and AuIn₂ crystal surfaces¹³ used in this study has been described in detail elsewhere.^{7,13} Both crystal surfaces were oriented to within 1° of the (001) plane using Laue x-ray diffractometry. The earlier study showed that in the case of AuGa₂, after alternating cycles of argon ion bombardment at energies from 3 keV to 500 eV and annealing to 575 K, a sharp LEED pattern, which was interpreted in terms of two perpendicular domains with a $(\sqrt{2} \times \sqrt{18})R45$ reconstruction, was seen. This same surface reconstruction was also observed for AuIn₂ (001) in this study. Although AES measurements were not available during the ARPES experiments, sharp LEED spots with no streaking or splitting and the absence of photoemission features in the valence band caused by oxygen or carbon indicated that both samples were free of contamination.

III. Results

Fig. 1 shows a set of normal emission ARPES spectra that were collected from the AuGa_2 (001) $(\sqrt{2} \times \sqrt{18})R45$ reconstructed surface. Various sets of features have been connected with lines and labeled A-G. Of these features, only two (A and B) show substantial dispersion as the photon energy is increased. The peaks labeled A correspond to photoemission from an s-p band that rises steeply between Γ and X, crossing the Fermi level before reaching Γ . Feature B is only seen at low photon energies (16-20 eV). These two sets of features are broader than the others through the entire range of photon energies used in this experiment. The other five features show relatively little dispersion, which is indicative of d-bands (in this case, mostly Au 5d in character).

ARPES spectra were also collected after the AuGa_2 sample was exposed to ~ 180 L of O_2 . The feature labeled F was much more sensitive to this contamination than any of the other features, in that a small amount of adsorbed oxygen was sufficient to reduce the intensity of feature F to below a detectable limit. Off-normal ARPES spectra of the clean surface were collected in order to observe the dispersion of any features with the parallel component of momentum (k_{\parallel}). Feature F was the only peak in the d-band region to exhibit noticeable dispersion of this type.

Fig. 2 consists of a set of normal emission spectra from the (001) $(\sqrt{2} \times \sqrt{18})R45$ surface of AuIn_2 . Features are once again connected and labeled A-E. These spectra are less complicated than those of AuGa_2 , since the features corresponding to B and E in Fig. 1 are missing. However, the AuIn_2 spectra show even more clearly the dispersion of the s-p band

(feature A). The other four features (labeled B-E) apparently correspond to Au 5d-like bands. Feature D in the AuIn₂ spectra dispersed in energy with varying $k_{||}$ in a manner very similar to that of feature F in the AuGa₂ spectra.

Fig. 3 contains a set of two spectra for each compound, which clearly show the sharp spin-orbit split d levels of Ga (3d) and In (4d). Table I lists the binding energies and the spin-orbit splittings for Ga 3d and In 4d for the Au intermetallic compounds compared with other materials. The binding energies for the Ga 3d or In 4d levels in each series of materials agree with one another to within 0.1 eV, which demonstrates that chemical shifts in these systems are small. The core levels shown in Fig. 3 also indicate the total energy resolution of the ARPES spectra.

IV. Discussion

The data were analyzed using the direct-transition model. The momentum component parallel to the surface ($k_{||}$) is conserved during the exit of the photoelectron through the surface. The normal momentum (k_{\perp}) is changed during the exit since the photoelectron has to cross an energy barrier. Since neither the conduction band structure nor the wavevector of the photoemitted electron are known in advance, k of the photoemitted electron inside the solid must be estimated. Assuming a free-electron conduction band structure (i.e. plane-wave final states), the normal component of the photoemitted electron momentum inside the crystal is given by:

$$k_{\perp, \text{in}}^2 = \frac{2m^*}{\hbar^2} [E_k + V_0 - E_k \sin^2 \theta] \quad (1)$$

where E_k is the kinetic energy of the photoelectron in the vacuum, θ is the polar angle of emission with respect to the sample normal, V_0 is the inner potential, which is assumed to be independent of kinetic energy, and m^* is the effective mass of the photoelectron. The values of the inner potential used for AuGa_2 and AuIn_2 were estimated to be 11.16 eV and 11.41 eV respectively, which were taken to be the difference between the muffin-tin zero of energy in the APW calculations¹¹ and the vacuum level as determined from the work functions of the two compounds. The experimental band structure along the Δ line was then found by plotting the binding energy of the photoelectron (relative to the Fermi level) versus k_{\perp} determined using Eq. 1, for various values of m^* . These plots were then compared to the non-relativistic band structures of Switendick and Narath,¹¹ but the

agreement was poor for all values of m^* , especially with respect to the d -bands.

Whenever the direct transition model is used to interpret ARPES, the limitations of the model must be considered in order to assess the level of agreement between theory and experiment. More specifically, situations that lead to the breakdown of momentum selection rules and result in uncertainty in \underline{k} must be examined. The effect of the inherent angular and energy resolution of the electron analyzer, the crystal momentum broadening of the photoelectron final states that results from finite mean free path lengths,¹⁴ and any broadening attributable to the Debye-Waller factors of the system must be carefully evaluated.¹⁵

Due to the dispersion of the initial state bands, changes in the momentum space region sampled in ARPES can cause very large changes in observed photoelectron energy distribution curves (EDC). The actual width of features observed in ARPES spectra depends upon both the resolution with which final momentum states are sampled and the energy dispersion of the initial state bands. This effect is quite evident in Fig. 2, where the s - p band at low binding energy is much broader than the d -level bands at higher binding energy. In general, s - p bands disperse much more rapidly than the almost flat d bands, thus accounting for the relative width of the features seen in the ARPES spectra.

The volume of the crystal momentum space sampled in an ARPES spectrum depends primarily upon the angular resolution of the electron analyzer and the crystal momentum broadening in the photoemission final state. The angular and energy resolution discussed in Sec. II result in an

instrumental broadening of k_{\perp} of 0.23 \AA^{-1} , or 11% of the BZ dimensions. The broadening due to the final state width is inversely proportional to the photoelectron mean free path (λ) and the angle (θ) between the momentum vector and the surface normal.¹⁶ Using the inelastic mean free path (IMFP) formula of Seah and Dench,¹⁷ and assuming an average photoelectron kinetic energy of 20 eV, the electron mean free path of AuGa₂ and AuIn₂ is calculated to be 6.8 Å. Thus, the expected k_{\perp} -broadening is 0.30 \AA^{-1} in both AuGa₂ and AuIn₂, which agrees well with the observed uncertainty in the momentum (0.31 \AA^{-1}) estimated from the full-width at half-maximum (FWHM) of the s-p photoemission peak A of AuIn₂ in Fig. 2 and the E versus k_{\parallel} dispersion of the calculated A_1 valence band.¹¹ This value corresponds to a final state FWHM momentum broadening which is 15% of the BZ dimensions. The total volume of k-space sampled in each spectrum of the present ARPES measurements caused by the angular resolution of the analyzer and the uncertainty in k_{\perp} may be estimated as a cylinder with a volume of 0.015 \AA^{-3} , which corresponds to 0.3% of the volume of the BZ. Although this may appear to be a rather small sampling volume of momentum space, it is responsible for the broad photoemission peaks from s-p like bands.

The last important broadening mechanism to be considered is thermal broadening due to indirect or phonon-assisted transitions. Such contributions to the uncertainty in momentum can best be estimated by looking at the Debye-Waller factors for each system. The bulk Debye temperatures of AuGa₂ and AuIn₂ are 196 K and 187 K, respectively.¹⁸ A rough estimate of the the mean-squared vibrational amplitude of each atom in the compounds was obtained using average atomic masses of 112.1 (AuGa₂) and 142.2 (AuIn₂) and the bulk Debye temperatures. The resulting values of

the Debye-Waller factor for AuGa_2 and AuIn_2 are 0.84 and 0.88, respectively. These numbers represent a modest contribution (~15%) of indirect transitions to the spectra and show that the direct transition model is still justified in these systems. To reduce the effect of lattice vibrations on the spectra, the samples could be cooled to liquid nitrogen temperatures, at which the Debye-Waller factors would be approximately 0.96 (AuGa_2) and 0.97 (AuIn_2). To appreciably improve the spectra, the sampling volume of momentum space would also have to be decreased substantially by using an ARFES analyzer with much better angular resolution and higher photon energies to increase the mean free paths of the photoelectrons.

Although not negligible, the momentum broadening effects discussed above are not serious enough to invalidate the direct transition model as applied to the photoemission spectra of AuGa_2 and AuIn_2 . Thus, the disagreement between the theoretical APW bands¹¹ and the experimentally determined bands is largely the result of the inaccuracies in the calculation. One major omission in the APW calculation was neglect of spin-orbit coupling,¹¹ which should be relatively large for Au 5d orbitals. Also, the binding energy positions with respect to E_F of the centroids of the d-bands were over-estimated by about 1 eV, and the d-band widths (even discounting the neglect of spin-orbit effects) were severely underestimated.¹²

In order to obtain a better theoretical estimate of the d-bands in AuGa_2 and AuIn_2 , a mixed basis interpolation scheme including spin-orbit splitting was developed for fluorite structure compounds.¹² The

non-relativistic APW bands of AuGa_2 and AuIn_2 were fit using this procedure. Then, using an estimate of the binding energies of the d-bands at Γ obtained from the direct transition model with $m^* = 1.0$ and the most intense photoemission features, the parameters of the interpolation scheme were adjusted to produce the three d-bands at Γ that agreed with those from the ARPES measurements. Next, the energy bands calculated from the ARPES spectra for various m^* values were compared with the interpolated bands, and reasonable agreement was found for $m^* = 1.25$. In principle, an iterative procedure could have been used in which a new set of binding energies for the d-bands at Γ would be determined for the new m^* value. However, for AuGa_2 and AuIn_2 , the d-bands were so flat that this was not necessary.

Figure 4(a) shows the energy bands of Au calculated by the interpolation scheme, using parameters from Ref. 12, as well as the interpolated and experimentally determined bands of AuGa_2 and AuIn_2 . By comparing Figs. 4(a), 4(b), and 4(c), one can see that the splitting of the Au 5d-levels is almost identical in each case, though the absolute binding energies are somewhat different. The spacing of the Au 5d bands at Γ can be used to determine the "crystal field" (Δ) and the spin-orbit (ζ) parameters, in the manner of Vehner, et al.¹⁰ These parameters, which are only meaningful at Γ , where the crystal momentum is zero, can be used to compare the relative strengths of d-orbital interactions and the spin-orbit coupling. Using the energy eigenvalues calculated by Ballhausen,¹⁹ ζ and Δ can be extracted from the ARPES data and compared to the same parameters for elemental Au. Table II consists of experimental and theoretical determinations of Δ and ζ for the series Au, AuGa_2 and AuIn_2 .

In the case of Au, previous experiments^{20,21} determined a Δ value of 1.22 eV and a spin-orbit parameter of 0.71 eV, which are in good agreement with the same parameters extracted from theoretical band structures.²² However, the experimental values of Δ for AuGa₂ and AuIn₂ are much larger than the non-relativistic d -band splitting calculated by Switendick and Narath,¹¹ and are essentially identical to one another, whereas the APW calculations predicted a substantial decrease in Δ for AuIn₂ with respect to AuGa₂. This observation is very surprising, since the Au d - d overlap integrals which give rise to the splittings at Γ (in the LCAO sense of Slater and Koster²³) should decrease dramatically in the series Au, AuGa₂ and AuIn₂ (as the APW results predict¹¹). The large crystal field effect in the intermetallic compounds may arise from interactions of the Au $5d$ orbitals with the d -orbitals of the group III metals (Ga $3d$ or In $4d$). The Au $5d$ -bands of AuAl₂ should be mapped in detail to test this hypothesis. Since Al has no occupied d -orbitals, one might expect the "crystal field" splitting to be much smaller for AuAl₂ than for AuGa₂ or AuIn₂. In fact, the total width of the AuAl₂ d -bands is smaller than for AuGa₂, as shown in the valence band XPS spectra.⁶ The spin-orbit parameter, which should essentially be a property only of the Au $5d$ orbitals, is very similar for all three systems.

The width of the d -bands of Au is broadened considerably by mixing with the lowest energy plane-wave band, as shown in Fig. 4(a). Since the lattice constants of AuGa₂ and AuIn₂ are so much larger than for Au, the BZ dimensions are much smaller. In the case of the two intermetallic compounds, the plane-wave band reaches the BZ boundary at X before it can cross the d -bands, as shown in Figs. 4(b) and (c). Thus, the d -bands of

AuGa_2 and AuIn_2 essentially reside within a bandgap in the plane-wave bands, and do not mix with the highly dispersing state. This allows the d -band width of the Au density of states to be much larger than for AuGa_2 and AuIn_2 , even though the d -band splitting at Γ is nearly the same for all three materials.

In addition to the conservation of momentum conditions, there exist uniquely solid state selection rules in ARPES that deal with final states observed along symmetry directions.²⁴ Since an ARPES experiment chooses a particular final state (which has particular symmetry properties), the initial states that may be sampled are determined by the radiation polarization with respect to the crystalline axes of the sample. In the case of normal photoemission from a (001) surface of a crystal with T_d symmetry and ignoring relativistic effects, the final state symmetry must be A_1 in order for the photoemitted electron to reach the detector. This requires the initial state to have either A_2 or A_1 symmetry,²⁴ both of which are allowed by the experimental geometry chosen for this experiment. These symmetry selection rules are only rigorous for detection systems with infinitely good angular resolution, but they provide a basis for analysis of ARPES with good angular resolution.

These selection rules will be used in analyzing photoemission from the s - p valence bands that reside to the lower binding energy side of the d -bands, since spin-orbit effects were not included in the interpolation scheme for the s - p bands. Feature A in the AuGa_2 spectra (Fig. 1) is caused by transitions from an s - p band between Γ and X. Unfortunately, its position with respect to the calculated bands (Fig. 4(b)) is such that it

is not possible to determine if the transition originates from an A_1 or A_2 initial state, since the experimental points essentially fall between two calculated bands. Photoemission from the flat A_2 band is not allowed by the selection rule, and in fact no peak corresponding to this band is observed in any of the ARPES spectra. This observation is actually somewhat surprising, since the selection rules are not expected to be completely rigorous, and the flat band should yield an extremely high density of initial states to be sampled.

The $AuBa_2$ features labeled B, which only appears at photon energies between 16 and 20 eV, are the result of a surface Umklapp process from a region of the BZ with the form: $\underline{k}=(1/3,1/3,X)$. There exists a surface reciprocal lattice vector $\underline{g}=(-1/3,-1/3,0)$ arising from the $(\sqrt{2} \times \sqrt{18})R45$ reconstructed surface which has the correct magnitude and direction to diffract photoelectrons emitted from initial states in this region of the BZ to the direction $(0,0,X)$, which can reach the electron energy analyzer in the normal emission geometry. Peaks labeled E are also a result of this same Umklapp process. These assignments have been confirmed by generating the valence bands along $\underline{k}=(1/3,1/3,X)$ in the BZ using the interpolation scheme and observing that valence bands exist with the correct binding energies and values of \underline{k} . Features C, D, and G in the $AuBa_2$ spectra have been assigned to the three d-levels that have symmetries (using relativistic notation) of Γ_8^+ , Γ_7^+ and Γ_9^+ , respectively. The d-bands are fairly flat, dispersing only a small amount between Γ and X, especially when compared to the corresponding d-bands of Au. The agreement between the dispersion of the interpolated and three experimental d-bands that were mapped out assuming a plane wave final state with $m^* = 1.25$ is qualitatively

correct, but differences of a few tenths of an eV exist as the bands approach X.

The final feature in the ARPES spectra is in a d-band gap along A in AuGa_2 . Feature F, which has a binding energy of ~ 6.2 eV, lies between the lower Γ_8^+ and Γ_7^+ d-levels. These peaks show no dispersion as the photon energy is increased from 16 to 30 eV. In addition, these features are more sensitive to surface contamination than photoemission peaks assigned to bulk bands. Lastly, some dispersion was seen in this feature as the parallel component of the wavevector was increased from zero by moving the detector off-normal. As the polar angle of emission (θ) was increased, the direction of rotation was in the plane containing the [001] and [110] axes. This is equivalent to simultaneously rotating from Γ to J and Γ to J' in the rectangular surface BZ, shown in the inset of Fig. 5, since the surface reconstruction is assumed to contain two perpendicular domains in analogy with the Ge (001) 2×1 reconstruction. The square symbols in Fig. 5 illustrate the dispersion of feature F with $k_{||}$. In view of these observations, feature F was assigned as a surface state.

The ARPES spectra (Fig. 2) of AuIn_2 are simpler than for AuGa_2 . Four features, which arise from bulk valence band transitions, are seen in the AuIn_2 case. The features labeled A correspond to transitions from an s-p band which crosses the Fermi level about halfway between Γ and X. The agreement between this experimental band and the A_1 band calculated by the interpolation scheme (Fig. 4(c)) is good, so the A feature is assigned to the valence band with A_1 symmetry. Within the uncertainty in the momentum, the experiment and the theory agree quite well as to the binding energy of

the band at the X point, but the dispersion of the band is not in as good agreement.

Features B, C, and E in the AuIn₂ spectra result from transitions from d-bands with the same symmetry as those observed for AuGa₂. These bands show even less dispersion between Γ and X than AuGa₂, presumably because the Au-Au separation is larger in AuIn₂ and the orbital interactions of the neighboring atoms is smaller. The agreement of the three experimental d-bands with the interpolation scheme calculation is excellent over the entire region between Γ and X. AuIn₂ exhibits the same ($\sqrt{2} \times \sqrt{18}$)R45 reconstruction as AuGa₂, so it should not be surprising to find a similar surface state on the (001) surface of AuIn₂. Feature D in the AuIn₂ spectra (Fig. 2) shows the same behavior as feature F (Fig. 1) in the case of AuGa₂. It is more sensitive to surface contamination than any of the bulk features. It shows no dispersion for normal photoemission in the range of photon energies used in this experiment. However, feature D does disperse with $k_{||}$, as shown by the circles in Fig. 3. Therefore, this feature has also been assigned as a surface state.

It would be possible to unambiguously map out both the valence and conduction bands of these two compounds using the triangulation technique of collecting ARPES spectra from two different surfaces.²⁵⁻²⁷ If two features are seen at the same binding energy from two different surfaces, then the value of $k_{||}$ can be determined absolutely. This would provide the necessary information for plotting the E versus $k_{||}$ dispersion relations of both initial and final states without invoking a plane-wave final state approximation. The resulting experimental energy bands could then be used

in conjunction with the interpolation scheme to determine a truly
experimental band structure.

V. Conclusions

The ARPES spectra of AuGa₂ and AuIn₂ are reasonably simple, and all features in both sets of spectra can be assigned to either bulk or surface transitions. Using a plane-wave final state approximation, the d-bands of both compounds are in good agreement with an interpolation scheme calculation, which was fit to a first principles APW calculation and adjusted to agree with the experimental results only at the Γ point of the BZ. The experimental s-p bands do not agree with the interpolation scheme as well as the d levels. However, the spectral features of the s-p bands are much broader, causing a larger uncertainty in the crystal momentum. The AuGa₂ spectra are somewhat more complicated than in AuIn₂, in that they contain features due to surface Umklapp processes. Essentially identical surface states that reside in a band gap between Γ_7^+ and the lower Γ_8^+ energy positions in the valence bands have been found on the (001) surfaces of AuGa₂ and AuIn₂.

Surprisingly, the splittings of the Au 5d bands at Γ for AuGa₂ and AuIn₂ are nearly identical with each other and with elemental Au, despite the large difference in the Au-Au distances in the three systems. A satisfactory explanation of this observation requires further experiments and/or detailed ab initio calculations. The difference observed in the total d-band width of the two compounds arises because the d-bands of AuIn₂ disperse less than those of AuGa₂, whereas the d-bandwidth of Au is also broadened by mixing of the d-bands with a plane-wave state.

VI. Acknowledgements

The authors wish to thank R.J. Baughman of Sandia National Laboratories for supplying the AuGa_2 and AuIn_2 single crystals, and J.A. Yarnoff, T.C. Tsai and R. Bimenthal for assistance with the experimental measurements. This work was performed at the Stanford Synchrotron Radiation Laboratory, which is supported by the United States Department of Energy under grant No. DE-AC03-82ER13000, in cooperation with the Stanford Linear Accelerator Center. Support for this project was provided by the Office of Naval Research. ESW acknowledges the Camille and Henry Dreyfus Foundation for providing a Teacher-Scholar Grant and the Alfred P. Sloan Foundation for a Fellowship.

References

1. S.S. Vishnubhakti and J.P. Jan. *Philos. Mag.* 16, 45 (1967).
2. J.T. Longo, P.A. Schroder and D.J. Sellmeyer, *Phys. Rev.* 182, 658 (1969).
3. J.C. Abele, J.H. Brewer and M.H. Halloran, *Solid State Commun.* 9, 977 (1971).
4. P.D. Chan and D.A. Shirley, Electronic Density of States, edited by L.H. Bennet (U.S. GPO, Washington D.C., 1971), p.323.
5. S. Hufner, J.H. Wernick and K.W. West, *Solid State Commun.* 10, 1013 (1972).
6. P.M.Th.M. van Attekum, G.K. Wertheim, G. Crocelius and J.H. Wernick, *Phys. Rev.* B22, 3998 (1980).
7. J.G. Nelson, J.R. Lince, W.J. Gignac and R.S. Williams, *J. Vac. Sci. Tech.* A2, 534 (1984).
8. G.V. Hansson and S.A. Floodstrom, *Phys. Rev.* B17, 473 (1978).
9. J. Stohr, P.S. Wehner, R.S. Williams, G. Apai and D.A. Shirley, *Phys. Rev.* B17, 587 (1978).
10. P.S. Wehner, R.S. Williams, S.D. Kevan, D. Donley and D.A. Shirley, *Phys. Rev.* B19, 6164 (1979).
11. A.C. Switendick and A. Narath, *Phys. Rev. Lett.* 22, 1423 (1969).
12. S. Kim, J.G. Nelson and R.S. Williams, *Phys. Rev. B*, accepted for publication.
13. The AuGa₂ and AuIn₂ crystals used in this experiment were pieces from larger ingots which were grown by R.J. Baughman of Sandia National Laboratories, Albuquerque, New Mexico. For details of the growth of the crystals see: R.J. Baughman, *Mater. Res. Bull.* 7, 505 (1972).
14. G.D. Mahan, *Phys. Rev.* B2, 4334 (1970).
15. R.S. Williams, P.S. Wehner, J. Stohr and D.A. Shirley, *Phys. Rev. Lett.* 39, 302 (1977).
16. P.J. Feibelman, *Surf. Sci.* 46, 548 (1974).
17. M.P. Seah and V.A. Dench, *Surf. and Interface Analy.* 1, 2 (1979).
18. J.A. Raynes, *Phys. Lett.* 7, 114 (1963).

19. C.J. Ballhausen. Introduction to Ligand Field Theory .
(McGraw-Hill, 1962). p.118.
20. K.A. Mills, R.F. Davis, S.D. Kevan, G. Thorton and D.A. Shirley.
Phys. Rev. E22, 581 (1980).
21. Richard F. Davis, Ph.D. Thesis. University of California, 1981,
unpublished.
22. H. Eckhardt, L. Fritsche and J. Noffe. J. Phys. F. 14, 97 (1984).
23. J.C. Slater and G.F. Koster, Phys. Rev. 94, 1498 (1954).
24. J. Hermanson, Solid State Commun. 22, 9 (1977).
25. E.O. Kane, Phys. Rev. Lett. 12, 97 (1964).
26. H. Neddermeyer, Sol. State Commun. 40, 809, (1981).
27. M. Pessa, M. Lindross, H. Asonen and N.V. Smith, Phys. Rev. E25,
738 (1982).

Table I. Binding Energies^a of Ga 3d and In 4d levels.

	Ga 3d _{5/2}	Ga 3d _{3/2}	spin-orbit splitting
GaAs ^b	18.60	19.04	0.44
GaSb ^b	18.70	19.13	0.43
AuGa ₂ ^c	18.60	19.19	0.59

	In 4d _{5/2}	In 4d _{3/2}	spin-orbit splitting
In metal ^d	16.74	17.64	0.90
InSb ^e	16.71	17.65	0.94
AuIn ₂ ^c	16.83	17.74	0.90

(a) All values in eV. Estimated uncertainty is 0.1 eV.

(b) D.E. Eastman, T.C. Chang, P. Heilmann and F.J. Himpsel. Phys. Rev. Lett. 45, 656 (1980). (Binding energy relative to Fermi level)

(c) this work (Binding energy relative to Fermi level)

(d) R.A. Pollack, S.P. Kovalovsk, L. Ley and D.A. Shirley, Phys. Rev. Lett. 29, 274 (1972). (Binding energy relative to Fermi level)

(e) L. Ley, R.A. Pollack, F.R. McFeeley, S.P. Kovalovsk and D.A. Shirley, Phys. Rev. 19, 600 (1974). (Binding energy relative to Fermi level)

Table II. Binding Energies^a of Au 5d levels at Γ

	lattice constant (\AA)		$E(\Gamma_8^1)$	$E(\Gamma_7)$	$E(\Gamma_8^2)$	Δ	ξ
Au	4.08	exp. ^b	-3.55	-4.45	-5.90	1.23	0.71
		theo. ^c	-3.38	-4.33	-5.75	1.28	0.70
AuGa ₂	6.06	exp. ^d	-4.92	-5.68	-7.31	1.07	0.78
		theo. ^e	-6.88	-7.60	-7.60	0.72	—
AuIn ₂	6.50	exp. ^d	-4.72	-5.48	-7.05	1.06	0.75
		theo. ^e	-6.47	-6.94	-6.94	0.47	—

(a) All values in eV. Estimated uncertainty in the experimental binding energies is 0.1 eV.

(b) ref. 20

(c) ref. 22

(d) this work

(e) ref. 11

Figure Captions

(Fig. 1) ARPES spectra of clean AuGa₂ (001) ($\sqrt{2} \times \sqrt{18}$)R45 taken at normal emission with the sample at room temperature. The line labeled A shows the peaks that have been assigned to transitions from the second s-p band of AuGa₂. Features B and E have been assigned to a surface Umklapp process. Lines C, D and G indicate bulk transitions from the Au 5d spin-orbit split levels. Finally, the peaks labeled F, which lie in a band gap in AuGa₂ along A, have been assigned to a surface state.

(Fig. 2) ARPES spectra of clean AuIn₂ (001) ($\sqrt{2} \times \sqrt{18}$)R45 taken at normal emission with the sample at room temperature. The line labeled A shows peaks that have been assigned to transitions from the second s-p band of AuIn₂. Features B, C, and E correspond to the 5d bands, and D arise from surface state emission.

(Fig. 3) ARPES spectra of clean AuGa₂ and AuIn₂ that extend to higher binding energies to reveal the Ga 3d and In 4d levels.

(Fig. 4(a)) The band structure of elemental Au along A of the fcc-lattice Brillouin Zone. The bands were calculated using an interpolation scheme that will be described in detail elsewhere.¹² The parameters used in this calculation were determined from the position of the Au 5d bands at Γ as estimated from the normal emission ARPES data of Refs. 20 and 21.

(Fig. 4(b)) Band structure of AuGa₂ along A. The dotted lines were calculated by the same interpolation scheme that was used for elemental Au.

The initial state assignments of the photoemission transitions are shown as squares or circles corresponding to strong or weak features in the spectra of Fig. 1, respectively. For symbols where there are no vertical lines indicating the energy uncertainty in locating a peak in the ARPES spectrum, the height of the symbol corresponds to or exceeds the uncertainty in the measurement.

(Fig. 4(c)) Same as Fig. 4B, except for AuIn_2 . The squares and circles represent peaks in the spectra of Fig. 2.

(Fig. 5) The dispersion of the features assigned as surface states in AuGa_2 (squares) and AuIn_2 (circles) with $k_{||}$. Because the surface reconstruction consists of two perpendicular domains, $k_{||}$ varies simultaneously from Γ to J and Γ to J' (in the surface BZ) as the photoelectron emission angle is varied in the $[110]$ azimuth. The two perpendicular surface BZ are shown in the inset.

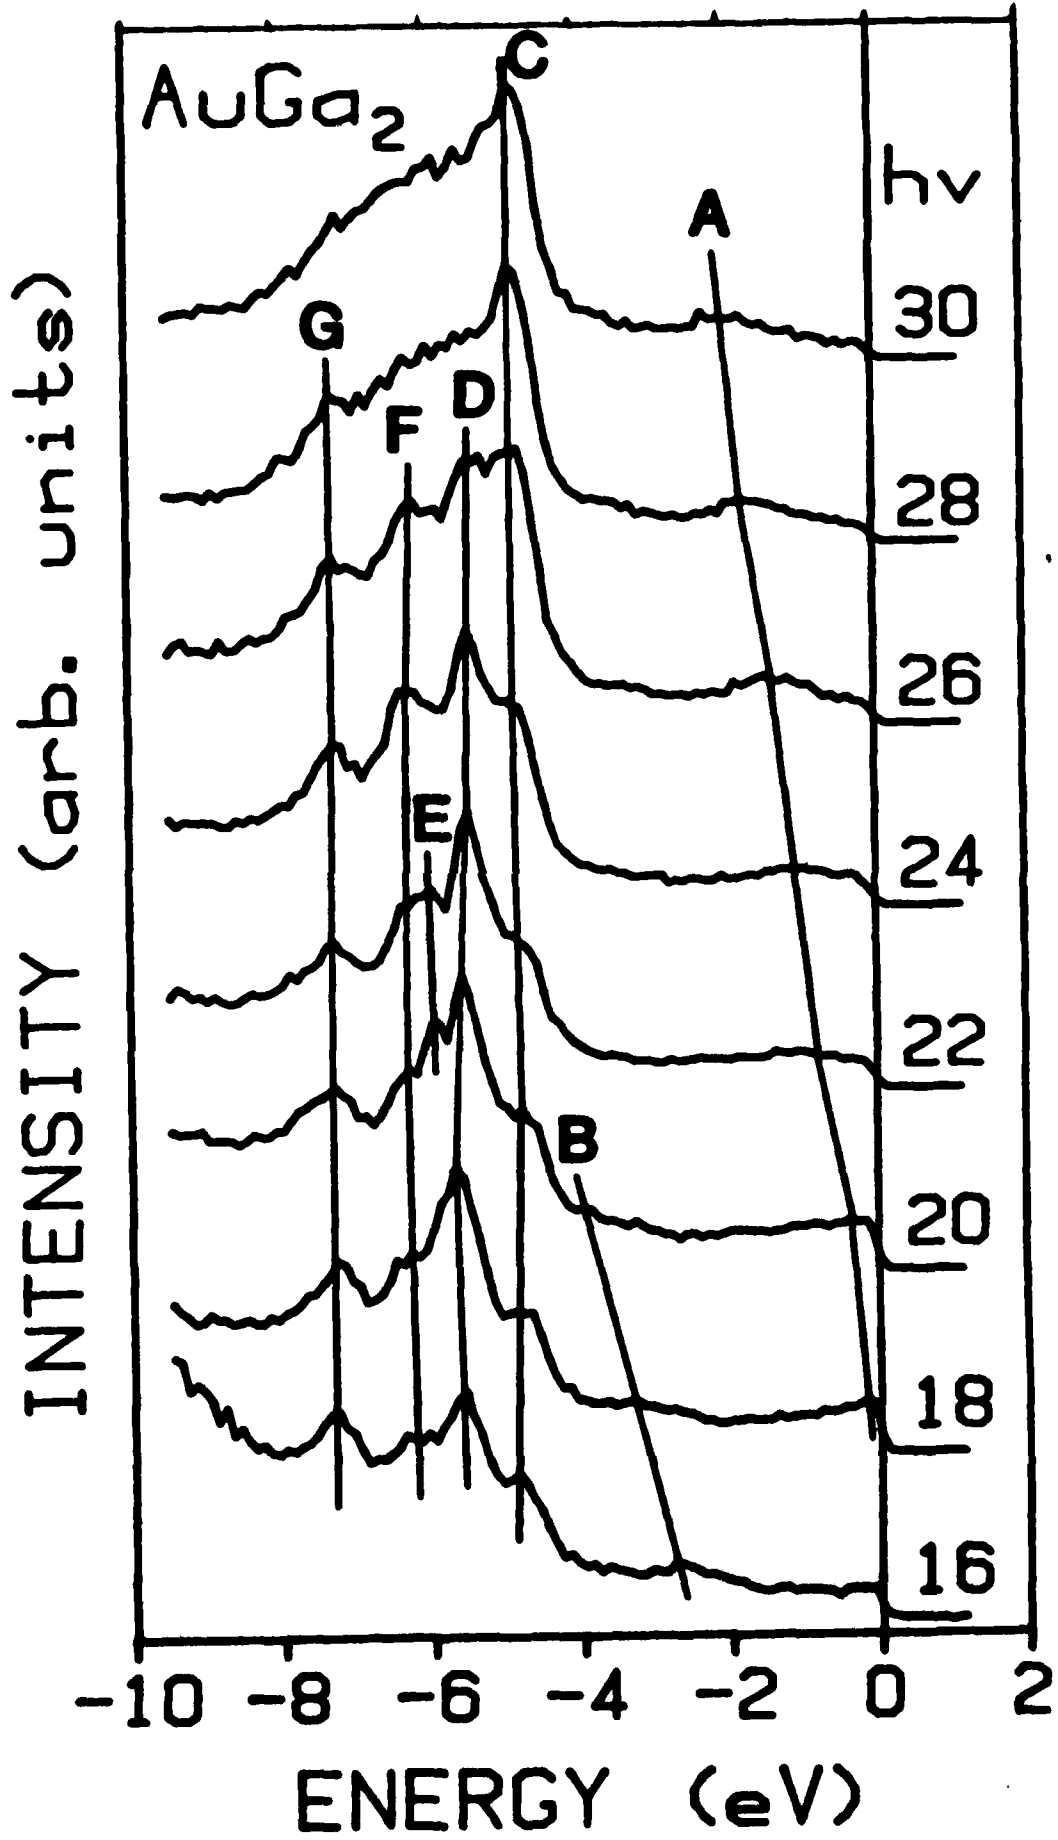


FIG. 1

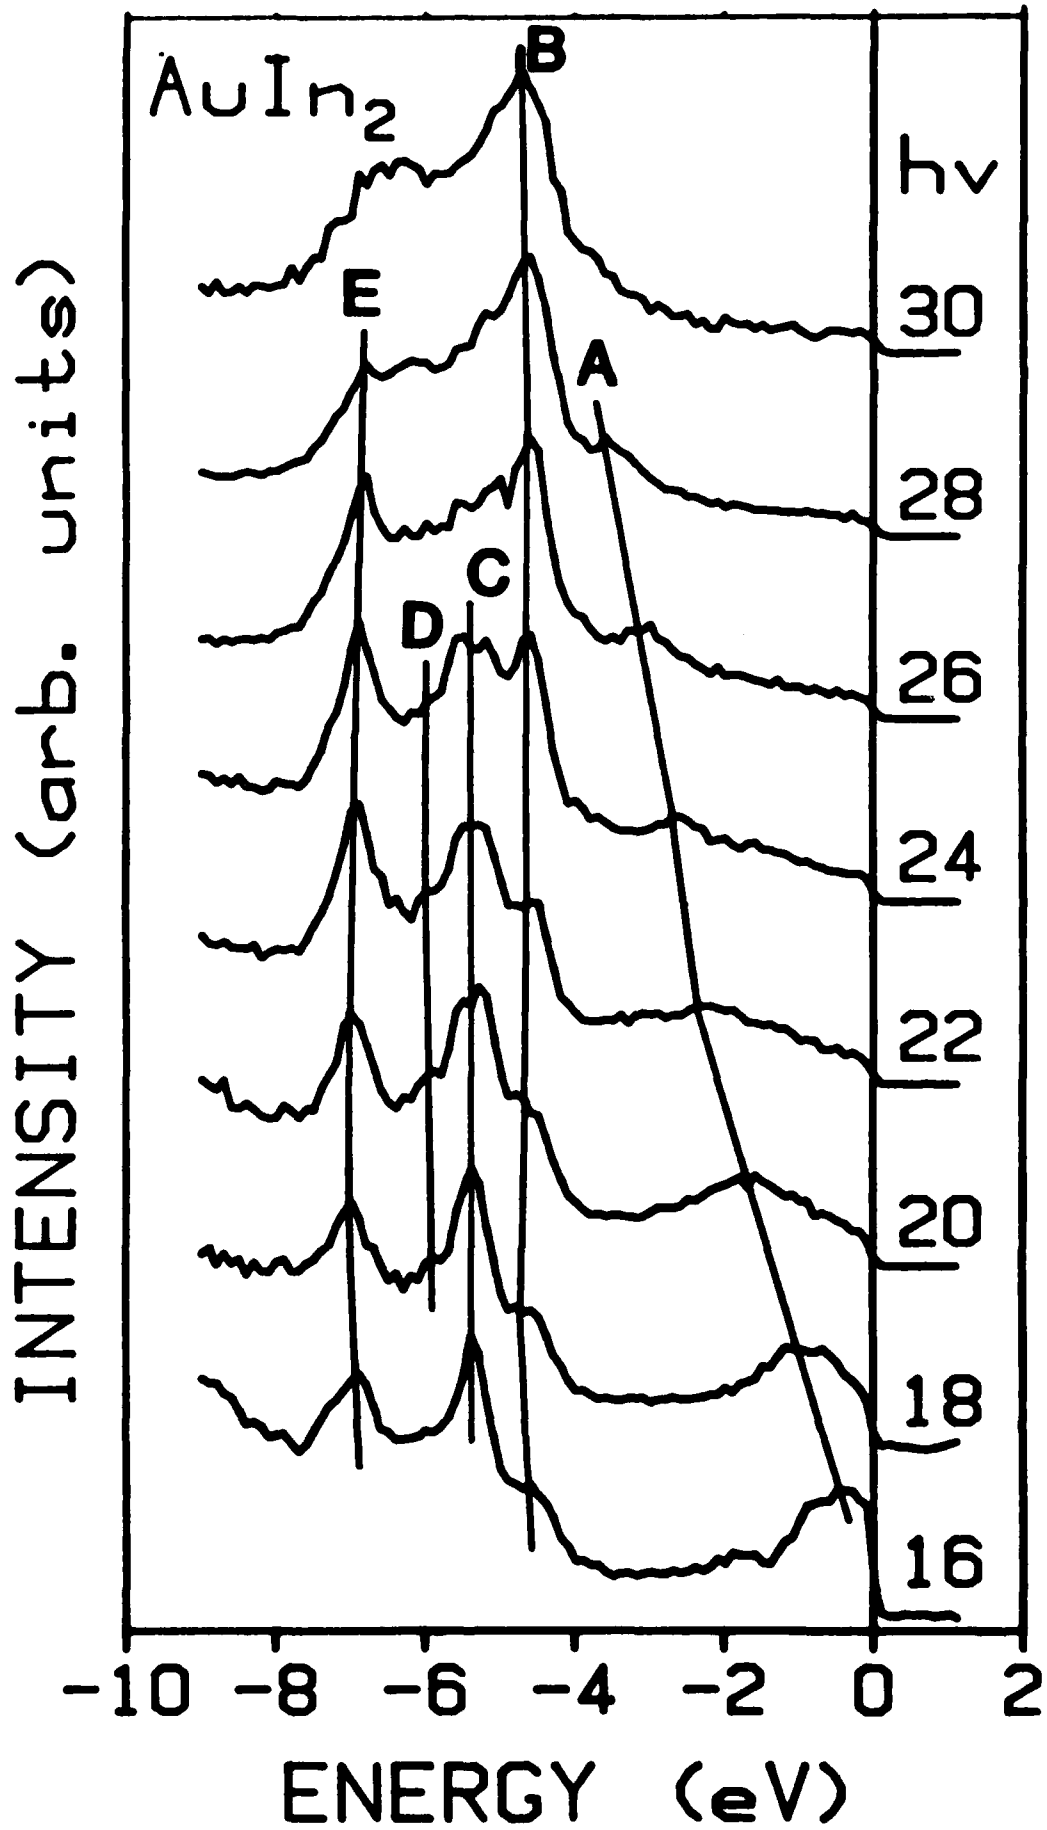


FIG. 2

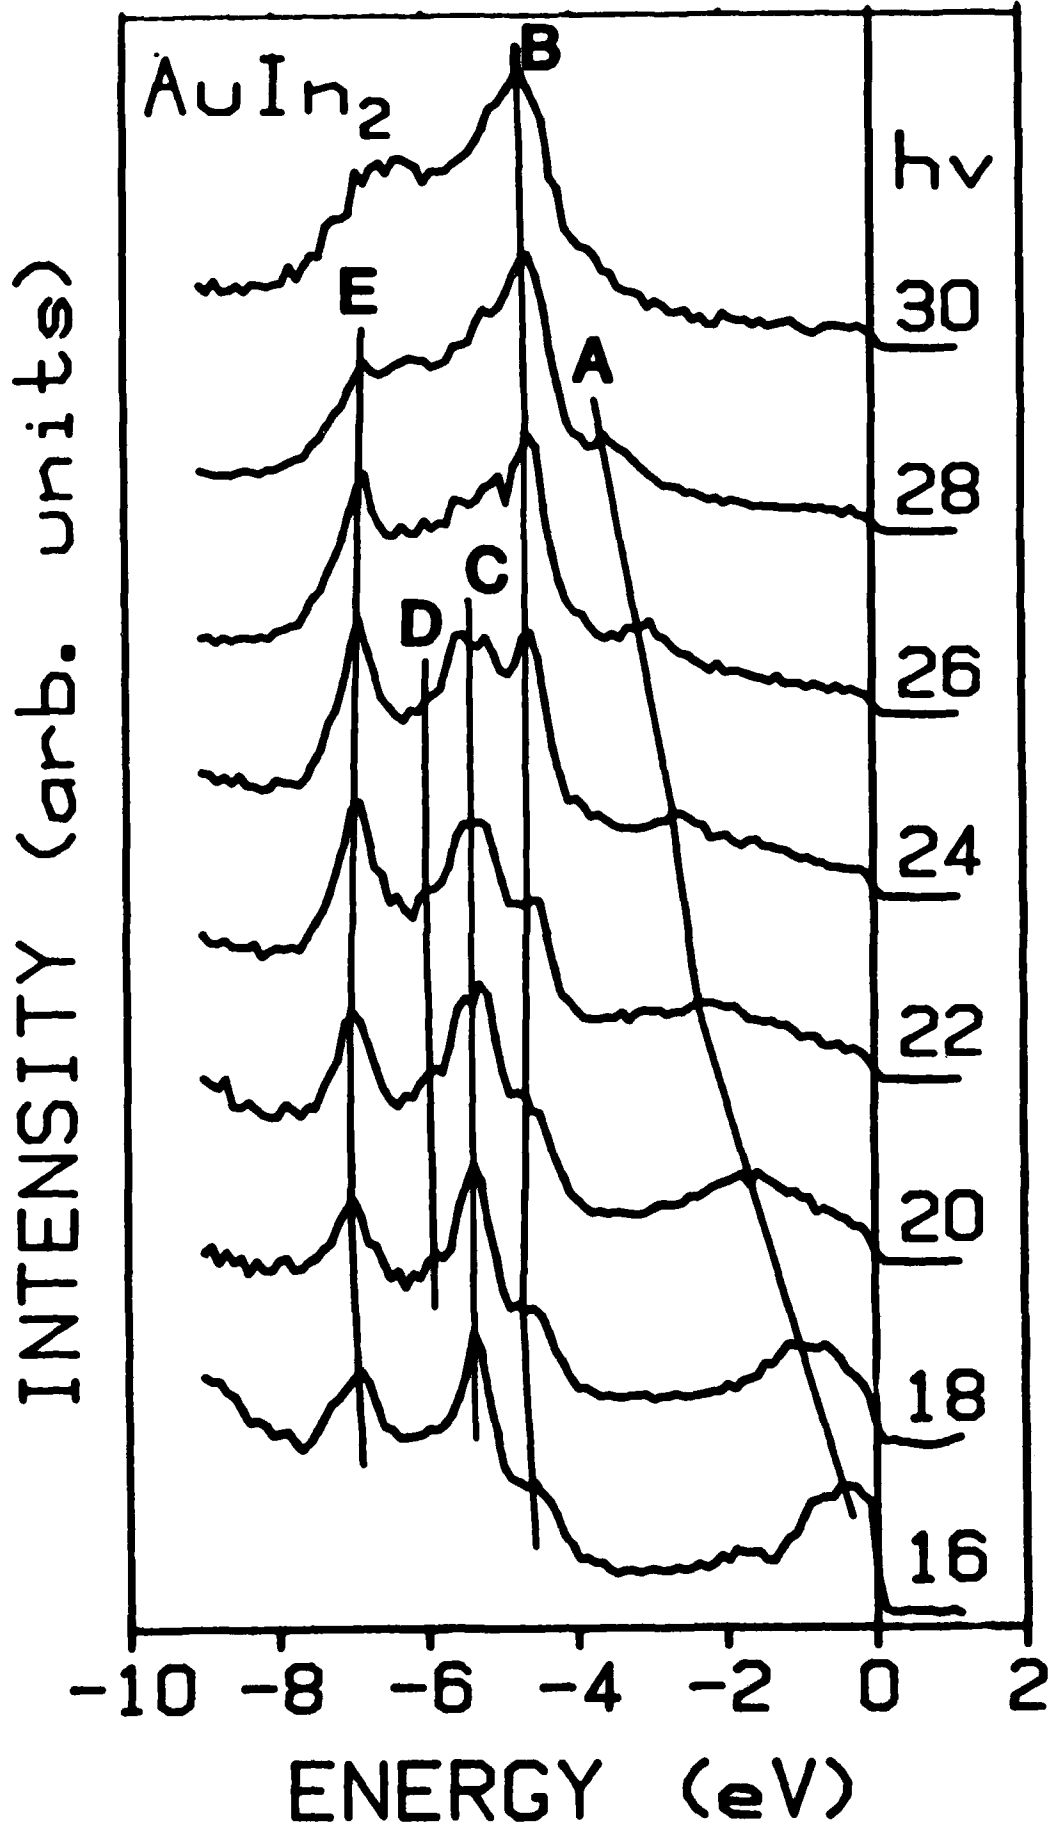


FIG. 2

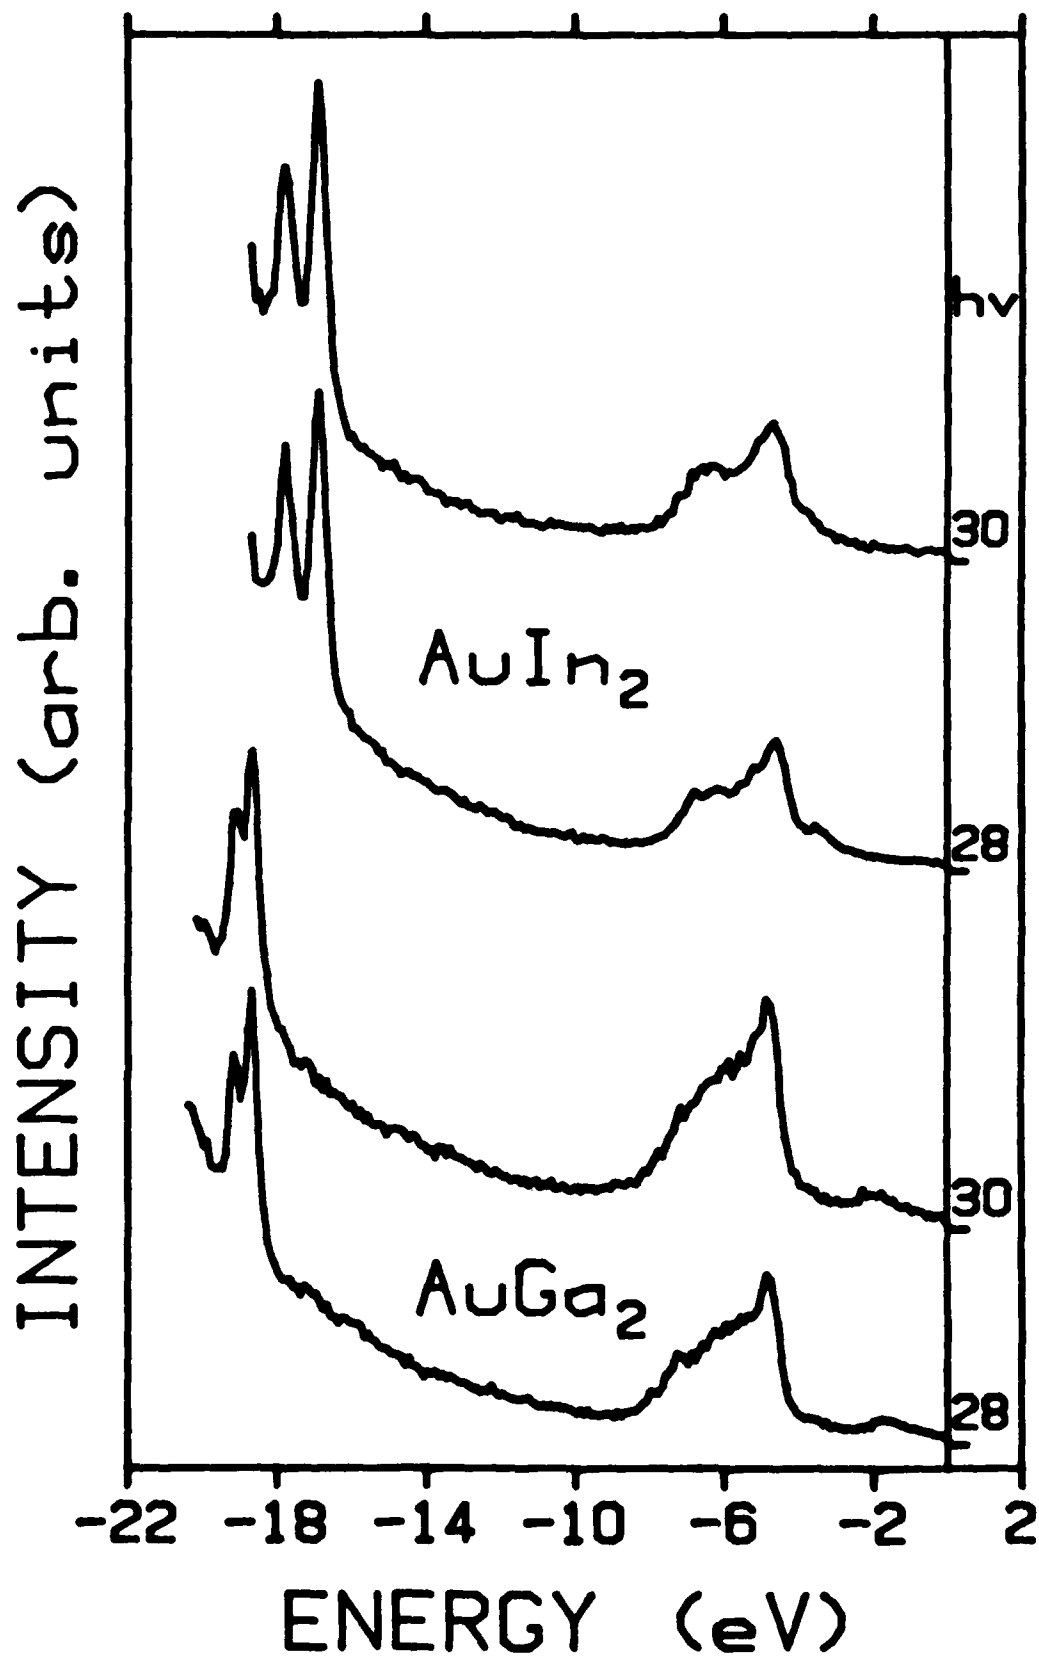


FIG. 3

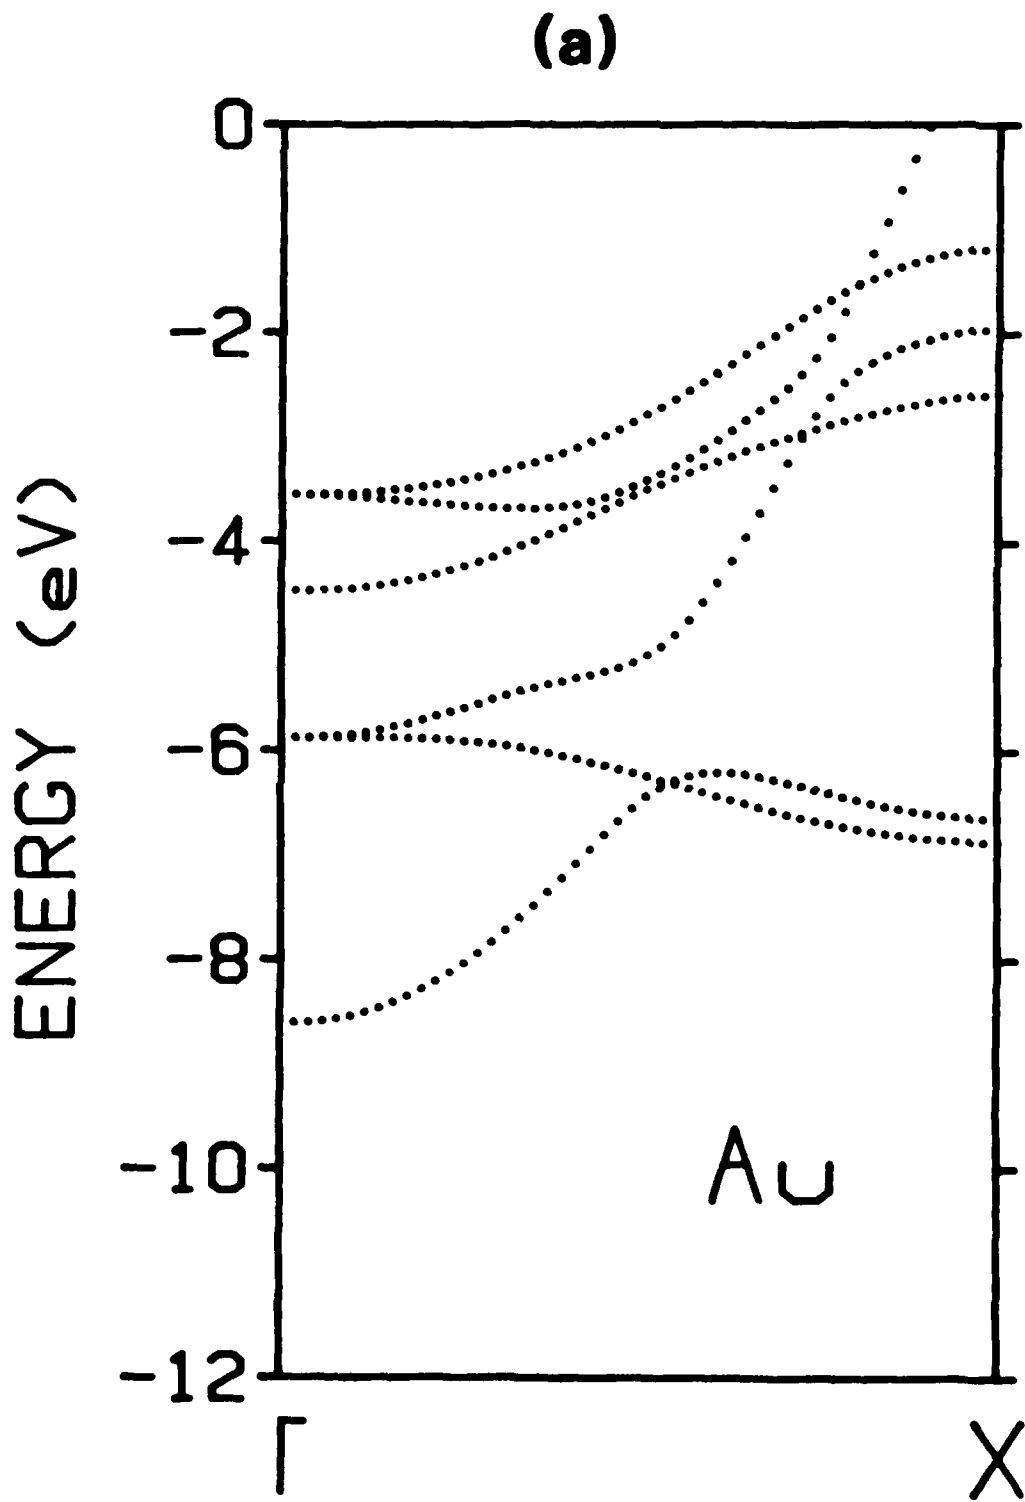


FIG. 4A

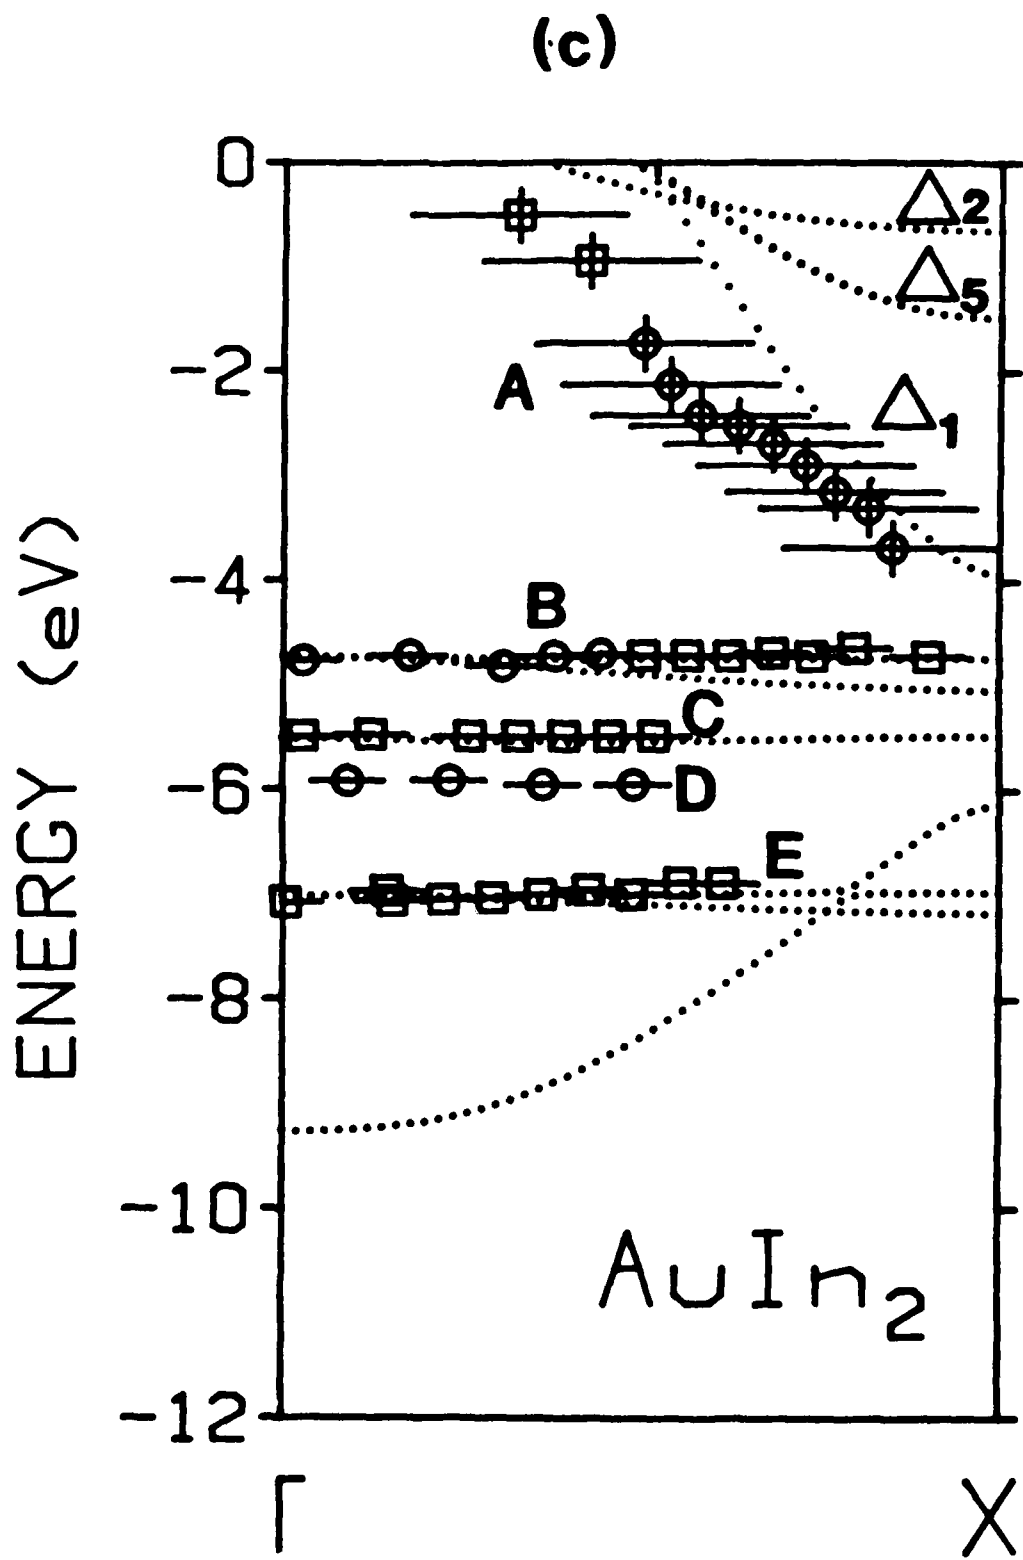


FIG. 4C

LATE
L MED
— 8





