



THE INFLUENCE OF CHEMICAL STRUCTURE ON THE STRENGTH OF RUBBER(U) AKRON UNIV OH INST OF POLYMER SCIENCE
A N GENT APR 86 TR-4 N00014-85-K-0222

1/1

F/G 11/10

NL

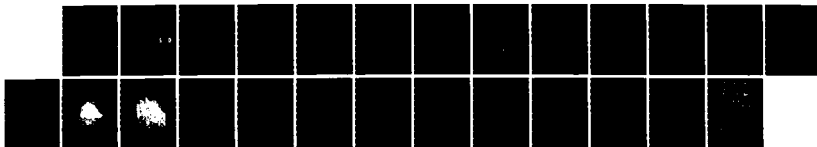

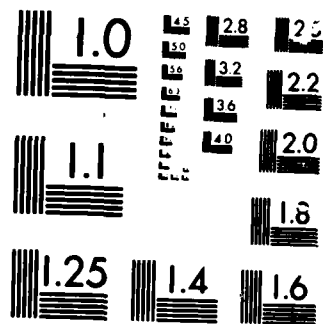

MICROCOPY RESOLUTION TEST CHART

AD-A166 355

12

OFFICE OF NAVAL RESEARCH

Contract N00014-85-K-0222

Project NR 092-555

Technical Report No. 4

THE INFLUENCE OF CHEMICAL STRUCTURE ON THE
STRENGTH OF RUBBER

by

A. N. Gent

Institute of Polymer Science
The University of Akron
Akron, Ohio 44325

April, 1986

Reproduction in whole or in part is permitted for
any purpose of the United States Government

Approved for Public Release; Distribution Unrestricted

DTIC
ELECTE
APR 09 1986
S D

DTIC FILE COPY

86 4 9 012

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 4	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) The Influence of Chemical Structure on the Strength of Rubber		5. TYPE OF REPORT & PERIOD COVERED Technical Report
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) A. N. Gent		8. CONTRACT OR GRANT NUMBER(s) N00014-85-K-0222
9. PERFORMING ORGANIZATION NAME AND ADDRESS Institute of Polymer Science The University of Akron Akron, Ohio 44325		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 092-555
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Power Program Arlington, VA 22217		12. REPORT DATE April, 1986
		13. NUMBER OF PAGES 22
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) According to attached distribution list. Approved for public release; distribution unrestricted.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Submitted for publication in: <u>Elastomers and Rubber Elasticity</u> , ed. by J. Lal and J.E. Mark. Plenum Publishing Corporation, New York.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Abrasion, Chemical structure, Crosslinking, Crystallization, Radicals, Reinforcement, Strain-induced crystallization, Strength, Tear Strength		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The detailed chemical structure of the polymer molecule has surpris- ingly little effect upon many of the important physical properties of crosslinked elastomers. For example, the elastic modulus, extensibility, tensile strength and tear strength are all much the same for many common elastomers. However, the strength of elastomers under some conditions is strikingly different. Two particular modes of fracture are considered here: tearing, and abrasive wear. Certain elastomers crystallize rapidly		

CONFIDENTIAL
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

on stretching and become self-reinforcing, so that their tear strength is greatly enhanced. Factors that govern the speed of strain-induced crystallization are reviewed. In abrasive wear, the macroradicals generated by molecular rupture are highly reactive and their reactions affect both the nature and the extent of wear. The wear processes that occur in various reinforced elastomers are described and compared.

S/N 0102- LF- 014- 6601

11
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

1. Introduction

Many of the physical properties of crosslinked elastomers do not depend directly upon the local chemical structure of the molecule at all. Instead, they depend upon other quantities, for example, the number ν of molecular strands per unit volume, upon their contour length L and mass M_c and upon the local rate ϕ of Brownian motion of molecular sub-units, consisting of small portions, about 5 main-chain atoms in length, of a molecular strand. (The actual number of main-chain atoms per molecular sub-unit is denoted q below; it is a measure of chain stiffness and hence it is somewhat smaller for more flexible molecules and larger for stiffer ones.) Some of these quantities are only indirectly related to the local molecular structure. As a result, many physical properties are found to be quite similar for elastomers that have markedly different chemical structure. For example, the tensile modulus of elasticity E for a network made up of flexible molecular strands is predicted by the statistical theory of rubber elasticity to be given by (1):

$$E = 3\nu kT \quad (1)$$

where k is Boltzmann's constant, and T is the absolute temperature. Although the analysis leading to equation 1 takes into account the limited flexibility of elastomer molecules, this feature of their chemical structure does not appear in the final result. Thus, whether the individual molecules are relatively stiff or relatively flexible is unimportant in so far as the elastic modulus of the network is concerned.

Even the maximum extensibility of the network is only slightly dependent upon the molecular flexibility, over the range that might be expected for simple elastomeric polymers. It is principally determined by the molecular length L , and hence molecular weight M_c between points of molecular interlinking (crosslinking) (1). It can be characterized by the ratio λ_m of the fully-stretched-out molecular length L to the average distance L_0 between the ends of molecular strands in the unstretched state. The former quantity is given by

$$L = n\ell \quad (2)$$

where n is the number of molecular sub-units in a molecular strand and ℓ is the length of a sub-unit. The latter quantity is given by

$$L_0 = n^{1/2}\ell \quad (3)$$

if it is assumed that the sub-units are connected together by freely-rotating joints. Thus,

$$\lambda_m = n^{1/2}, \quad (4)$$

where n is related to the number n_0 of main-chain atoms per molecular strand by

$$n = n_0/q, \quad (5)$$

to the molecular weight $\underline{M}_c$ of a network strand by

$$n = \underline{M}_c / q \underline{M}_o, \quad (6)$$

where $\underline{M}_o$ is the molecular weight per main-chain atom, and to the number $\underline{v}$ of network strands per unit volume by

$$n = A / \underline{v} q \underline{M}_o, \quad (7)$$

where A denotes Avogadro's number. Equations 4-7 show that $\underline{\lambda}_m$ depends upon $\underline{q}^{-1/2}$.

2. Tear Strength of Non-Crystallizing Elastomers

When elastomeric networks are torn apart under conditions of minimum strength, i.e., when no additional energy is expended in various dissipative processes (for example, viscous motion of molecular strands or detachment from filler particles), then the work $\underline{G}_{c,o}$ of fracture per unit area torn through is given by (2)

$$\underline{G}_{v,o} = \underline{v}' n_o \underline{U} \quad (8)$$

where $\underline{v}'$ is the number of strands crossing a randomly chosen plane of unit area (the fracture plane, for example) and $\underline{U}$ is the dissociation energy of a main-chain bond. The value of $\underline{v}'$ is directly related to the number $\underline{v}$ of strands per unit volume and the average distance $\underline{L}_o$ between their ends (2):

$$\underline{v}' = (3/8)^{1/2} \underline{v} \underline{L}_o \quad (9)$$

Thus, from equations 3, 7, 8 and 9:

$$\underline{G}_{c,o} = (3/8)^{1/2} \rho A \underline{U} q^{1/2} \underline{L}_o \underline{M}_c^{1/2} / \underline{M}_o^{3/2} \quad (10)$$

In terms of Young's modulus $\underline{E}$, from equations 1, 6 and 7:

$$\underline{G}_{c,o} = (9/8)^{1/2} (\rho A)^{3/2} (q k T)^{1/2} \underline{U} \underline{L}_o / \underline{M}_o^{3/2} \underline{E}^{1/2} \quad (11)$$

Equation 1 indicates, and experiments confirm, that the modulus of elasticity $\underline{E}$ depends primarily upon the number of network strands and not upon their detailed structure. On the other hand, equations 10 and 11 show that the tear strength depends significantly upon the mass $\underline{M}_o$ per main-chain atom, as well as upon the number of strands and hence $\underline{E}$. Experimental measurements of tear strength under threshold conditions, i.e., at high temperatures and low rates of tearing, are in good agreement with these theoretical predictions, as shown in Figures 1 and 2 (3). Values of the work of fracture $\underline{G}_c$ are found to increase in proportion to $\underline{M}_c^{1/2}$, and to decrease in proportion to $\underline{E}^{-1/2}$, for networks prepared by crosslinking to different degrees. And, for the same values of $\underline{M}_c$ or of $\underline{E}$, substantial differences are found between different polymers, those with larger values of mass $\underline{M}_o$ per main-chain atom having lower tear strengths, as low as 1/5 of the tear strength of the simple hydrocarbon elastomers.

QUALITY
INSPECTED
3

Codes

or

A-1

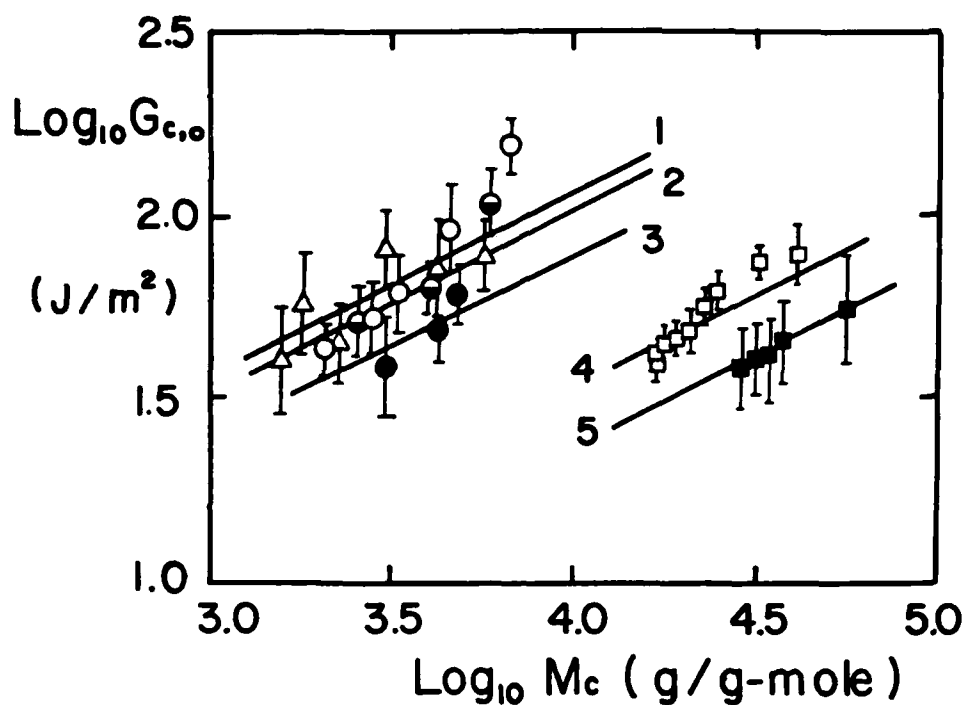


Fig. 1. Threshold tear strength $G_{c,o}$ vs. molecular weight M_c of network strands (3). 1, polybutadiene, $M_o=13.5a.m.u.$, (Δ); 2, cis-polyisoprene, $M_o=17a.m.u.$, ($\circ$); 3, trans-polyisoprene, $M_o=17a.m.u.$, ($\bullet$); 4, polydimethyl siloxane, $M_o=37a.m.u.$, ($\square$); 5, phosphonitrilic fluoroelastomer, $M_o=185a.m.u.$, ($\blacksquare$).

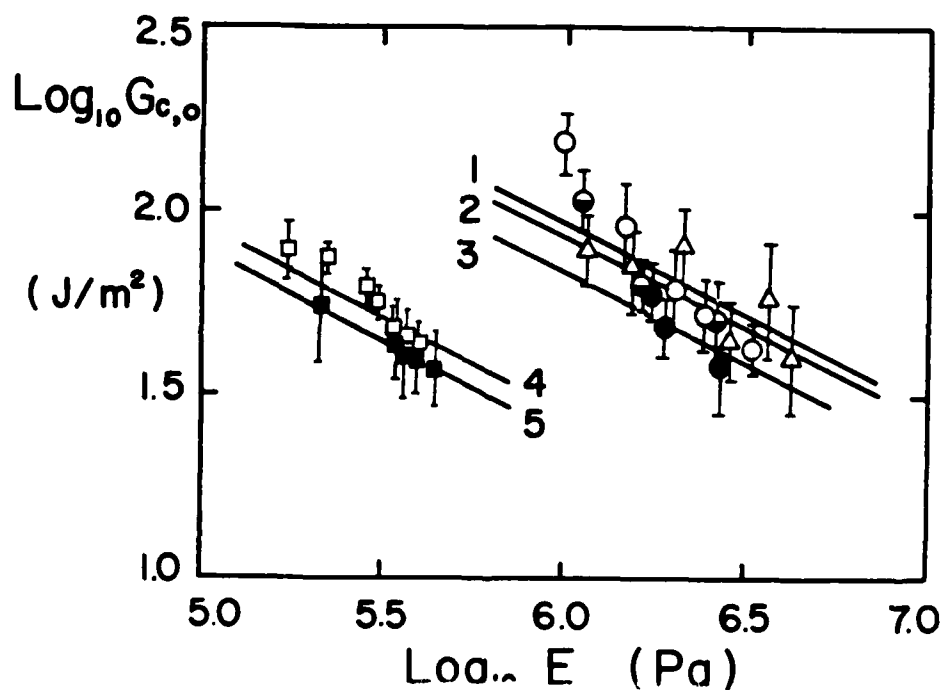


Fig. 2. Threshold tear strength $G_{c,o}$ vs. Young's modulus E (3). Symbols as in Figure 1.

Under normal conditions the tear strength is many times larger than the small threshold value $G_{c,0}$, about $50\text{--}100 \text{ J/m}^2$, because of energy expended in various dissipative processes. For simple viscoelastic materials the tear strength is governed by the local viscosity, i.e., by the rate ϕ of Brownian motion of molecular sub-units. In turn, ϕ is directly related to the temperature difference $T - T_g$, where T is the test temperature and T_g is the glass transition temperature of the elastomer (4):

$$\log_{10}(\phi_T/\phi_{T_g}) = 17.6(T - T_g)/(52 + T - T_g) \quad (12)$$

where ϕ_{T_g} denotes the rate of sub-unit motion at T_g , about 0.1 jumps/sec. Using a scaling factor $a_T = \phi_T/\phi_{T_g}$ for the rate of tearing, measurements of tear strength for several elastomers at many temperatures can be superimposed to give a master curve for tear strength as a function of the effective rate of tearing at T_g , Figure 3. This demonstrates that the tear strength depends only upon $T - T_g$, and not upon the local chemical structure of the elastomer except insofar as that determines the value of T_g (5).

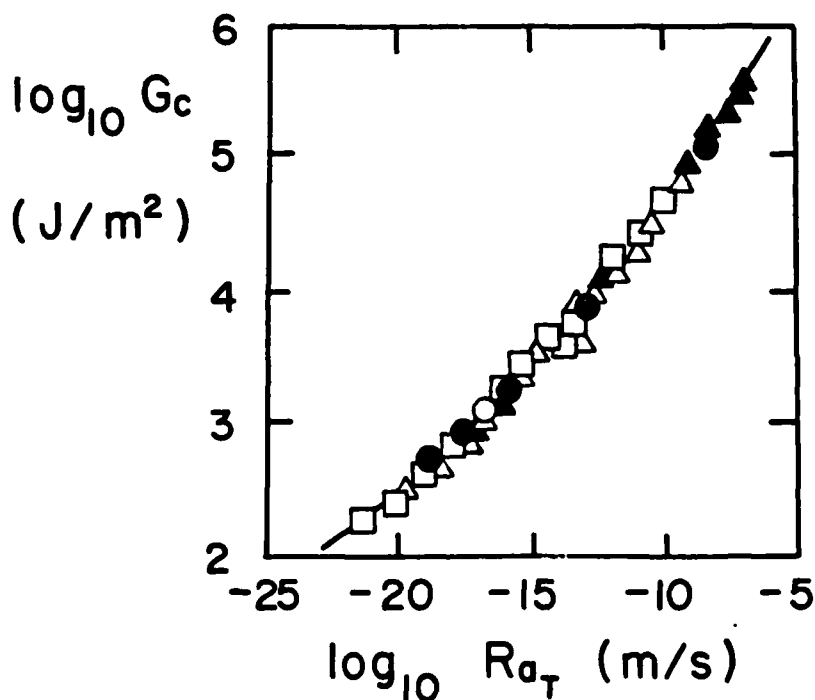


Fig. 3. Tear strength G_c plotted against the effective rate of tearing at T_g (5). Results are shown for six butadiene-styrene (SBR) and butadiene-acrylonitrile (NBR) elastomers, with T_g ranging from -30°C to -80°C .

Far above T_g , under threshold conditions, the tear strength depends significantly upon the molecular structure as discussed earlier, and there is some evidence that the same relative differences are maintained under non-equilibrium conditions. But the primary variable for determining the tear strength is $T - T_g$.

The question now arises; which fracture processes, if any, are strongly affected by the local chemical structure? Two examples are considered below: tearing and crack growth, and abrasive wear. Under certain conditions these failure processes are found to depend upon particular features of the elastomer molecule and they are therefore distinctly different, even for closely-related chemical structures. Natural rubber can usefully be compared with cis 1, 4-polybutadiene in this respect, because, although their chemical structures are superficially similar, large differences are observed in their resistance to tearing and in the mechanism of wear.

3: Tearing and Crack Growth in Strain-Crystallizing Elastomers

Certain elastomers, notably natural rubber, crystallize on being stretched by several hundred per cent. They become much stiffer, and rather inelastic due to delays in crystallization and in melting on release. At a crack tip, rubber is highly stressed even when the overall strain is relatively small. The loss of energy associated with crystallization and, later, melting in this region leads to enhanced tear strength at low rates and high temperatures (6), and a much improved resistance to crack growth under repeated stressing (7), as shown in Figures 4, 5 and 6, in comparison with a non-crystallizing elastomer. Strain-induced crystallization is thus a specific, and highly desirable, feature of elastomers. The physical and chemical factors responsible for it are discussed below.

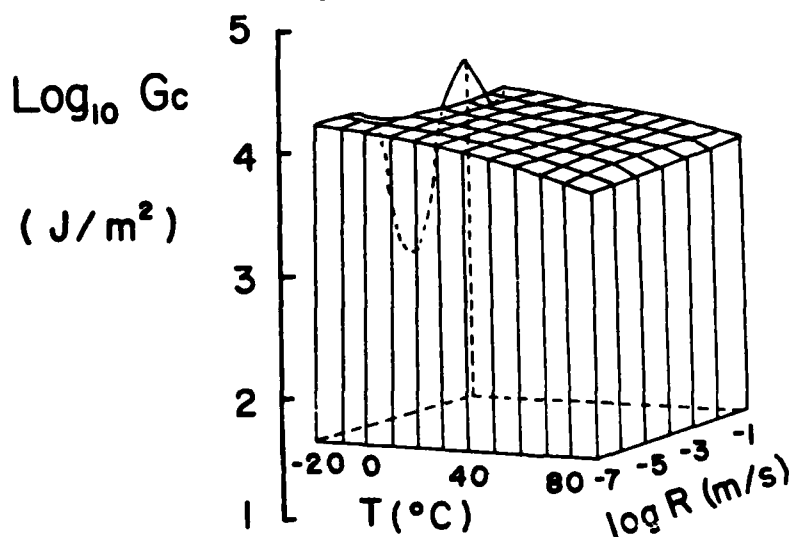


Fig. 4. Tear strength G_c of natural rubber as a function of test temperature T and rate R of tearing (6).

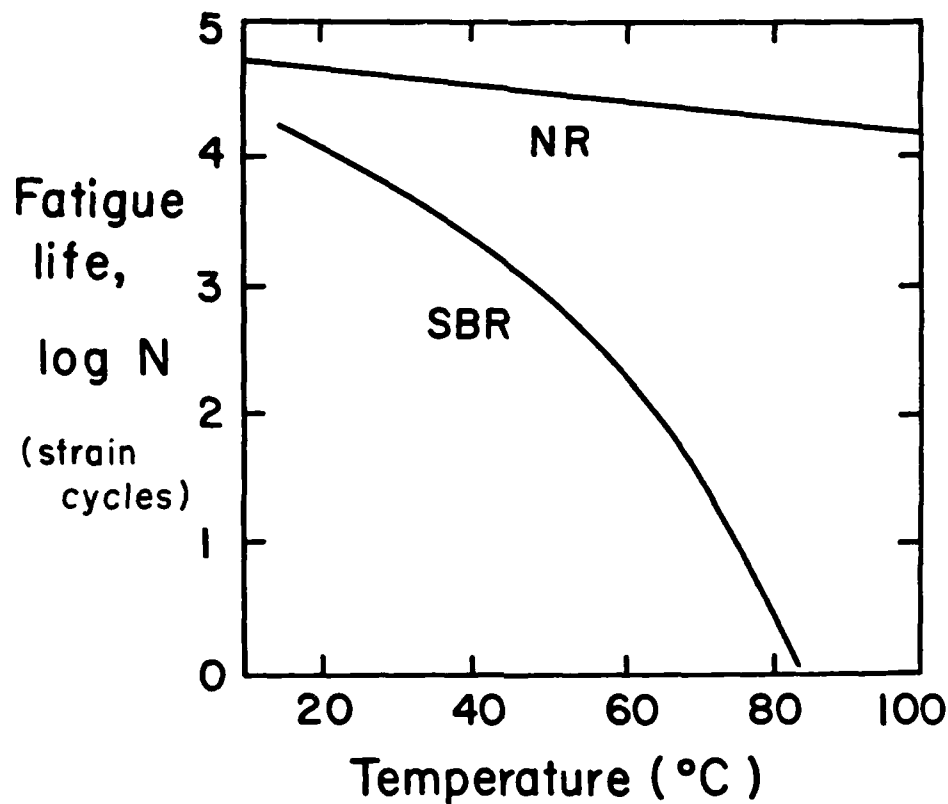


Fig. 5. Fatigue life $\underline{N}$ of natural rubber (NR) and a butadiene-styrene rubber (SBR) plotted against the test temperature $\underline{T}$ (7).

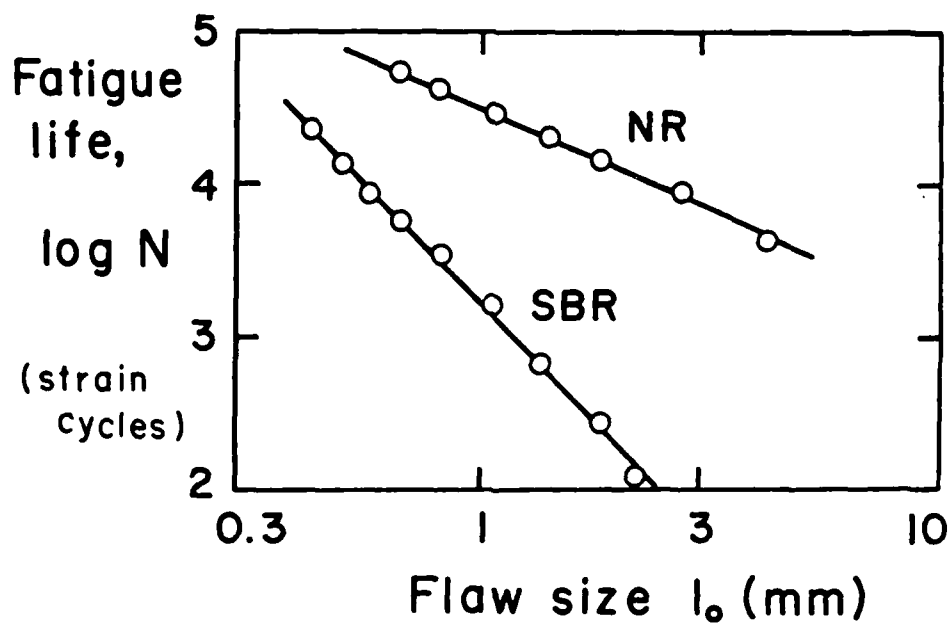


Fig. 6. Fatigue life $\underline{N}$ of natural rubber (NR) and a butadiene-styrene rubber (SBR) plotted against the depth $\underline{l}_0$ of an initial edge crack (7).

4. Strain-Induced Crystallization

8

The phenomenon of rapid crystallization in the strained state and rapid melting on release can be attributed to three main causes:

(i) In the unstrained state the crystal melting temperature T_m lies below ambient temperature and the material is therefore non-crystalline.

(ii) On stretching, the melting temperature is raised markedly, to values well above ambient, so that crystallization is thermodynamically favored and the free energy change on fusion is large.

(iii) The glass transition temperature T_g is quite low, well below ambient. Molecular sub-units are consequently highly mobile at ambient temperature and are able to enter the crystalline state rapidly when the free energy change is favorable.

Many polymers have low values of T_g and therefore satisfy condition (iii). However, many of them have either relatively large latent heats of fusion h or, more commonly (8), relatively small latent entropies of fusion s , so that their melting temperatures T_m , given by

$$T_m = h/s, \quad (13)$$

lie above ambient temperature. They are therefore normally crystalline in the unstrained state. Some common examples are: polyethylene, polyethylene oxide, trans 1, 4-polybutadiene and trans 1, 4-polyisoprene (see Table 1). These materials do not satisfy condition (i).

Table 1: Melting temperatures T_m and latent heats of fusion h for some representative crystallizing polymers.^a

	T_m ($^{\circ}\text{C}$)	h (kJ/kg)
Polyethylene	141	280
Polyethylene oxide	66	200
<u>Trans</u> 1, 4-polyisoprene	74	190
<u>Trans</u> 1, 4-polybutadiene	148	187
<u>Cis</u> 1, 4-polybutadiene	6	163
<u>Trans</u> 1, 4-polychloroprene	80	95
<u>Cis</u> 1, 4-polyisoprene	30	65

a Taken from reference 8 and "Physical Constants of Linear Homopolymers", by O. G. Lewis, Springer-Verlag, New York 1968.

Of the remaining elastomeric materials, some will meet condition (ii) more successfully than others. The reasons for this can be readily deduced from Flory's approximate theoretical treatment for the melting temperature $T_{m,\lambda}$ of crystallites in a molecular network held at a stretch ratio λ (9). A molecular sub-unit entering a crystallite from a strand in a stretched molecular network undergoes a smaller loss of configurational entropy than from the unstretched state because its configurational entropy has already been lowered somewhat by stretching. The reduction Δs in the entropy of fusion can be evaluated from the statistics of deformed and undeformed molecular networks. The result leads, by means of equation 13, to a predicted increase in the melting temperature on stretching (9):

$$(hQM_0/R) (T_m^{-1} - T_{m,\lambda}^{-1}) = (6/\pi n)^{1/2} \lambda - (\lambda^2 + 2\lambda^{-1})/2n \quad (14)$$

where h is the latent heat of fusion per gram, R is the gas constant, and λ is the tensile stretch ratio applied to the network. This relation is found to give reasonably satisfactory predictions of the melting temperatures $T_{m,\lambda}$ at moderate extensions, in the range 100 to 400 per cent ($\lambda = 2$ to 5) and for different degrees of crosslinking, represented by different values of the molecular strand length n . Some typical results are shown in Figures 7 and 8 (10,11).

Both calculated and observed increases in melting temperature on stretching are found to be larger for some elastomers than for others, and for natural rubber the effect is largest of all. The reason for this lies in the unusually small value of the latent heat of fusion h for cis-polyisoprene, Table 1. As equation 14 indicates, the increase in T_m on stretching is inversely related to h . Thus, the smaller the value of h the greater will be the tendency to exhibit strain-induced crystallization. An abnormally low value of h for natural rubber appears to be associated in part with the relatively small change in density that accompanies crystallization and in part with the absence of strong interatomic binding in the unit cell. Whatever the exact cause, the low value of h is clearly responsible for the facility with which natural rubber crystallizes on stretching.

5. Abrasive Wear

Wear of rubber under sliding conditions resembles small-scale tearing (12). Indeed, it has been treated as cumulative tearing - a mechanical fatigue process - taking place under the repeated action of frictional forces. A quantitative relationship has been derived in this way for the rate of wear in terms of the rate of crack growth under repeated stressing (13,14). When the rubber is rather tough and wear resistant, however, there is evidence of chemical deterioration during sliding, in addition

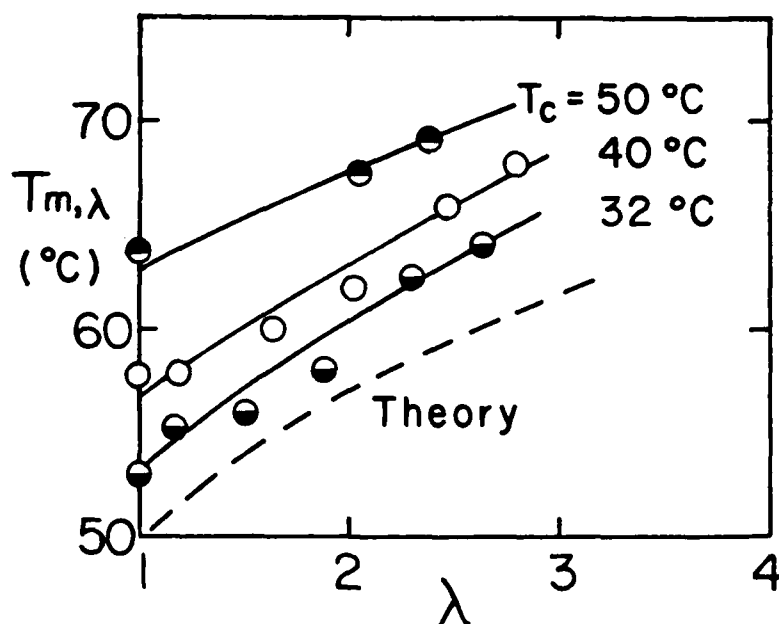


Fig. 7. Melting temperatures for crosslinked trans 1, 4-polychloroprene, held at various stretch ratios λ and crystallized at various temperatures T_c (10). Theoretical relation from equation 14 for increase in T_m with λ .

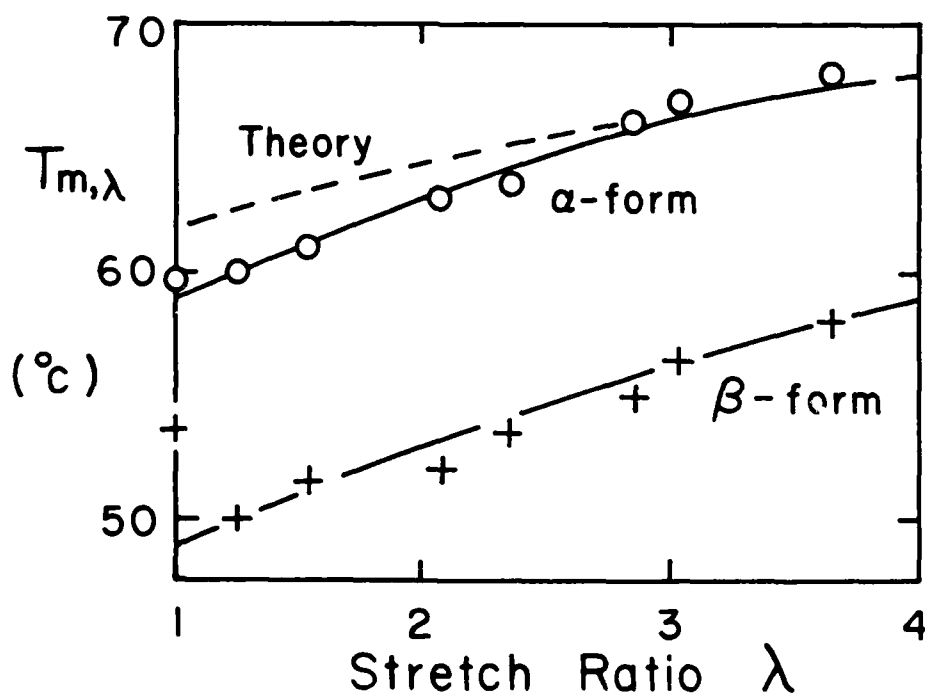


Fig. 8. Melting temperatures for crosslinked trans 1, 4-polyisoprene, held at various stretch ratios λ (11). Theoretical relation from equation 14 for increase in T_m with λ .

to tearing (15,16). When this deterioration is extensive the rubber and abrading surface become covered with an oily decomposition product and the tearing process is altered, if not stopped altogether.

An example of a particle of wear debris torn from a rather weak material, an unfilled butadiene-styrene (SBR) vulcanizate, is shown in Figure 9. It has characteristically rough, torn surfaces. In contrast, the particle shown in Figure 10, obtained from a carbon-black-filled SBR vulcanizate, has a smooth, shiny appearance and the surface is sticky, as if covered with an oily or tarry film. The debris from carbon-black-filled natural rubber vulcanizates is even more highly degraded, so that the individual particles can hardly be distinguished in this case. On the other hand, the debris from carbon-black-filled cis 1, 4-polybutadiene materials is finely-divided and particulate showing no signs of decomposition and every indication of having been mechanically torn away from the rubber surface. Thus, the wear process for reinforced elastomeric materials of roughly equal hardness and friction coefficient, and of comparable tear strength and tensile strength, differs strikingly in character from one polymer to another. These differences must be ascribed to different chemical features of the elastomers.

It should be pointed out at this stage that the formation of an oily degraded surface layer is not necessarily a beneficial feature. If the layer is readily removed from the rubber, then further deterioration can proceed rapidly. Indeed, if in the early stages of decomposition, the rubber is rendered softer and weaker, it will be torn away more easily and the rate of wear will be correspondingly greater than in the absence of general molecular scission. On the other hand, if the liquidlike film is viscous, tarry, and adhesive, it appears to be retained on the rubber surface to act as a protective layer. The rate of wear is then much reduced.



Fig. 9. Photograph of wear debris from an unfilled SBR vulcanizate.



Fig. 10. Photograph of wear debris from a carbon-black-filled SBR vulcanizate.

In order to account for the formation of a degraded surface film in some instances, a number of possible chemical processes can be hypothesized:

- (i) Thermal decomposition, as a result of frictional heating.
- (ii) Oxidative scission of the molecular network, possibly accelerated by frictional heating.
- (iii) Mechanical rupture of the molecular network, followed by internal and external reactions of the polymer radicals generated in this way.

The first process need not be considered further here, because all of these elastomers are more or less equally susceptible to thermal decomposition whereas they do not all degrade during sliding. The second process is also probably not the main mechanism of decomposition because some elastomers show frictional decomposition even in inert atmospheres (15). The third process, however, does appear to be the basic mechanism of molecular decomposition during sliding. A rather good correlation is found to hold between the degree of decomposition observed during frictional sliding, both in air and in an inert atmosphere, and corresponding changes in molecular weight when the original elastomer (before crosslinking) is subjected to continuous mechanical shearing (15,16). For example, polybutadiene forms rather reactive macroradicals by molecular scission, and then undergoes crosslinking reactions, so that both in the shearing of the uncrosslinked polymer and the frictional sliding of the reinforced and crosslinked polymer, the product of mechanochemical processes tends to become a crosslinked solid. In contrast, natural rubber forms a resonance-stabilized macroradical by molecular fracture, which, in the presence of oxygen, forms a peroxy radical and then a hydroperoxide by H abstraction so that the original chain fracture is rendered permanent. Indeed, subsequent oxidation steps may cause scission of other chains as well. Thus, the product of mechanical rupture of the molecular network in this case tends to become liquidlike rather than solid.

These considerations account for the formation of a viscous liquid film on certain materials, and not on others, during frictional sliding. Moreover, the properties of the film, its viscosity and adhesiveness, will clearly depend upon the detailed reactions initiated by mechanical rupture of the elastomer molecules. They will therefore differ from one elastomer to another and they will also depend upon the particular ingredients used in the rubber mix formulation, especially when these substances are themselves able to participate in free-radical reactions.

Many of the differences encountered in the wear behavior of practical rubber compounds can thus be accounted for in a qualitative way when the specific chemical process involved in wear is recognized.

Acknowledgements

This review was prepared in the course of a research program supported by the Office of Naval Research (Contract No. N00014-85-K-0222). An earlier version was presented at the conference Natural rubber: Towards The Year 2000, held in Saltillo, Mexico, July 7-11, 1980, under the auspices of the Centro de Investigacion en Quimica Aplicada. The author is indebted to Dr. C.T.R. Pulford of the Goodyear Tire and Rubber Company Research Laboratories for his helpful comments.

References

1. L. R. G. Treloar, "Physics of Rubber Elasticity", 2nd. Ed., Oxford University Press, London, 1958.
2. G. J. Lake and A. G. Thomas, Proc. Roy. Soc. London A300, 108 (1967).
3. A. N. Gent and R. H. Tobias, J. Polymer Sci., Polymer Phys. Ed. 20, 2051 (1982).
4. J. D. Ferry, "Viscoelastic Properties of Polymers", 3rd. Ed., Wiley, New York, 1980.
5. L. Mullins, Trans. Inst. Rubber Industry 35, 213 (1959).
6. H. W. Greensmith and A. G. Thomas, J. Polymer Sci. 18, 189 (1955).
7. G. J. Lake and P. B. Lindley, Rubber J. Internatl. Plastics 146 (10), 24 (1964); 146 (11), 30 (1964).
8. L. Mandelkern, "Crystallization of Polymers", McGraw-Hill, New York, 1964.
9. P. J. Flory, J. Chem. Phys. 15, 397 (1947).
10. A. N. Gent, J. Polymer Sci. A3, 3787 (1965).
11. A. N. Gent, J. Polymer Sci., Part A2 4, 447 (1966).
12. A. Schallamach, Rubber Chem. Technol. 41, 209 (1968).
13. A. G. Thomas, J. Polymer Sci: Symposium No. 48, 145 (1974).
14. E. Southern and A. G. Thomas, Plastics and Rubber: Materials and Applications 3 (4), 133 (1978).
15. A. N. Gent and C. T. R. Pulford, J. Materials Sci. 14, 1301 (1979).
16. A. N. Gent and C. T. R. Pulford, J. Appl. Polymer Sci. 28, 943 (1983).

(DYN)

DISTRIBUTION LIST

Dr. R.S. Miller
Office of Naval Research
Code 432P
Arlington, VA 22217
(10 copies)

Dr. J. Pastine
Naval Sea Systems Command
Code 06R
Washington, DC 20362

Dr. Kenneth D. Hartman
Hercules Aerospace Division
Hercules Incorporated
Alleghany Ballistic Lab
P.O. Box 210
Washington, DC 21502

Mr. Otto K. Heiney
AFATL-DLJG
Elgin AFB, FL 32542

Dr. Merrill K. King
Atlantic Research Corp.
5390 Cherokee Avenue
Alexandria, VA 22312

Dr. R.L. Lou
Aerojet Strategic Propulsion Co.
Bldg. 05025 - Dept 5400 - MS 167
P.O. Box 15699C
Sacramento, CA 95813

Dr. R. Olsen
Aerojet Strategic Propulsion Co.
Bldg. 05025 - Dept 5400 - MS 167
P.O. Box 15699C
Sacramento, CA 95813

Dr. Randy Peters
Aerojet Strategic Propulsion Co.
Bldg. 05025 - Dept 5400 - MS 167
P.O. Box 15699C
Sacramento, CA 95813

Dr. D. Mann
U.S. Army Research Office
Engineering Division
Box 12211
Research Triangle Park, NC 27709-2211

Dr. L.V. Schmidt
Office of Naval Technology
Code 07CT
Arlington, VA 22217

JHU Applied Physics Laboratory
ATTN: CPIA (Mr. T.W. Christian)
Johns Hopkins Rd.
Laurel, MD 20707

Dr. R. McGuire
Lawrence Livermore Laboratory
University of California
Code L-324
Livermore, CA 94550

P.A. Miller
736 Leavenworth Street, #6
San Francisco, CA 94109

Dr. W. Moniz
Naval Research Lab.
Code 6120
Washington, DC 20375

Dr. K.F. Mueller
Naval Surface Weapons Center
Code R11
White Oak
Silver Spring, MD 20910

Prof. M. Nicol
Dept. of Chemistry & Biochemistry
University of California
Los Angeles, CA 90024

Mr. L. Roslund
Naval Surface Weapons Center
Code R10C
White Oak, Silver Spring, MD 20910

Dr. David C. Sayles
Ballistic Missile Defense
Advanced Technology Center
P.O. Box 1500
Huntsville, AL 35807

(DYN)

DISTRIBUTION LIST

Mr. R. Geisler
ATTN: DY/MS-24
AFRPL
Edwards AFB, CA 93523

Naval Air Systems Command
ATTN: Mr. Bertram P. Sobers
NAVAIR-320G
Jefferson Plaza 1, RM 472
Washington, DC 20361

R.B. Steele
Aerojet Strategic Propulsion Co.
P.O. Box 15699C
Sacramento, CA 95813

Mr. M. Stosz
Naval Surface Weapons Center
Code R10B
White Oak
Silver Spring, MD 20910

Mr. E.S. Sutton
Thiokol Corporation
Elkton Division
P.O. Box 241
Elkton, MD 21921

Dr. Grant Thompson
Morton Thiokol, Inc.
Wasatch Division
MS 240 P.O. Box 524
Brigham City, UT 84302

Dr. R.S. Valentini
United Technologies Chemical Systems
P.O. Box 50015
San Jose, CA 95150-0015

Dr. R.F. Walker
Chief, Energetic Materials Division
DRSMC-LCE (D), B-3022
USA ARDC
Dover, NJ 07801

Dr. Janet Wall
Code 012
Director, Research Administration
Naval Postgraduate School
Monterey, CA 93943

Director
US Army Ballistic Research Lab.
ATTN: DRXBR-IBD
Aberdeen Proving Ground, MD 21005

Commander
US Army Missile Command
ATTN: DRSMI-RKL
Walter W. Wharton
Redstone Arsenal, AL 35898

Dr. Ingo W. May
Army Ballistic Research Lab.
ARRADCOM
Code DRXBR - 1BD
Aberdeen Proving Ground, MD 21005

Dr. E. Zimet
Office of Naval Technology
Code 071
Arlington, VA 22217

Dr. Ronald L. Derr
Naval Weapons Center
Code 389
China Lake, CA 93555

T. Boggs
Naval Weapons Center
Code 389
China Lake, CA 93555

Lee C. Estabrook, P.E.
Morton Thiokol, Inc.
P.O. Box 30058
Shreveport, Louisiana 71130

Dr. J.R. West
Morton Thiokol, Inc.
P.O. Box 30058
Shreveport, Louisiana 71130

Dr. D.D. Dillehay
Morton Thiokol, Inc.
Longhorn Division
Marshall, TX 75670

G.T. Bowman
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

(DYN)

DISTRIBUTION LIST

R.E. Shenton
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

Mike Barnes
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

Dr. Lionel Dickinson
Naval Explosive Ordinance
Disposal Tech. Center
Code D
Indian Head, MD 20340

Prof. J.T. Dickinson
Washington State University
Dept. of Physics 4
Pullman, WA 99164-2814

M.H. Miles
Dept. of Physics
Washington State University
Pullman, WA 99164-2814

Dr. T.F. Davidson
Vice President, Technical
Morton Thiokol, Inc.
Aerospace Group
110 North Wacker Drive
Chicago, Illinois 60606

Mr. J. Consaga
Naval Surface Weapons Center
Code R-16
Indian Head, MD 20640

Naval Sea Systems Command
ATTN: Mr. Charles M. Christensen
NAVSEA-62R2
Crystal Plaza, Bldg. 6, Rm 806
Washington, DC 20362

Mr. R. Beauregard
Naval Sea Systems Command
SEA 64E
Washington, DC 20362

Brian Wheatley
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

Mr. G. Edwards
Naval Sea Systems Command
Code 62R32
Washington, DC 20362

C. Dickinson
Naval Surface Weapons Center
White Oak, Code R-13
Silver Spring, MD 20910

Prof. John Deutch
MIT
Department of Chemistry
Cambridge, MA 02139

Dr. E.H. deButts
Hercules Aerospace Co.
P.O. Box 27408
Salt Lake City, UT 84127

David A. Flanigan
Director, Advanced Technology
Morton Thiokol, Inc.
Aerospace Group
110 North Wacker Drive
Chicago, Illinois 60606

Dr. L.H. Caveny
Air Force Office of Scientific
Research
Directorate of Aerospace Sciences
Bolling Air Force Base
Washington, DC 20332

W.G. Roger
Code 5253
Naval Ordnance Station
Indian Head, MD 20640

Dr. Donald L. Ball
Air Force Office of Scientific
Research
Directorate of Chemical &
Atmospheric Sciences
Bolling Air Force Base
Washington, DC 20332

(DYN)

DISTRIBUTION LIST

Dr. Anthony J. Matuszko
Air Force Office of Scientific Research
Directorate of Chemical & Atmospheric
Sciences
Bolling Air Force Base
Washington, DC 20332

Dr. Michael Chaykovsky
Naval Surface Weapons Center
Code R11
White Oak
Silver Spring, MD 20910

J.J. Rocchio
USA Ballistic Research Lab.
Aberdeen Proving Ground, MD 21005-5066

G.A. Zimmerman
Aerojet Tactical Systems
P.O. Box 13400
Sacramento, CA 95813

B. Swanson
INC-4 MS C-346
Los Alamos National Laboratory
Los Alamos, New Mexico 87545

Dr. James T. Bryant
Naval Weapons Center
Code 3205B
China Lake, CA 93555

Dr. L. Rothstein
Assistant Director
Naval Explosives Dev. Engineering Dept.
Naval Weapons Station
Yorktown, VA 23691

Dr. M.J. Kamlet
Naval Surface Weapons Center
Code R11
White Oak, Silver Spring, MD 20910

Dr. Henry Webster, III
Manager, Chemical Sciences Branch
ATTN: Code 5063
Crane, IN 47522

Dr. A.L. Slafkosky
Scientific Advisor
Commandant of the Marine Corps
Code RD-1
Washington, DC 20380

Dr. H.G. Adolph
Naval Surface Weapons Center
Code R11
White Oak
Silver Spring, MD 20910

U.S. Army Research Office
Chemical & Biological Sciences
Division
P.O. Box 12211
Research Triangle Park, NC 27709

G. Butcher
Hercules, Inc.
MS X2H
P.O. Box 98
Magna, Utah 84044

W. Waesche
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

Dr. John S. Wilkes, Jr.
FJSRL/NC
USAF Academy, CO 80840

Dr. H. Rosenwasser
AIR-320R
Naval Air Systems Command
Washington, DC 20361

Dr. Joyce J. Kaufman
The Johns Hopkins University
Department of Chemistry
Baltimore, MD 21218

Dr. A. Nielsen
Naval Weapons Center
Code 385
China Lake, CA 93555

(DYN)

DISTRIBUTION LIST

K.D. Pae
High Pressure Materials Research Lab.
Rutgers University
P.O. Box 909
Piscataway, NJ 08854

Dr. John K. Dienes
T-3, B216
Los Alamos National Lab.
P.O. Box 1663
Los Alamos, NM 87544

A.N. Gent
Institute Polymer Science
University of Akron
Akron, OH 44325

Dr. D.A. Shockey
SRI International
333 Ravenswood Ave.
Menlo Park, CA 94025

Dr. R.B. Kruse
Morton Thiokol, Inc.
Huntsville Division
Huntsville, AL 35807-7501

G. Butcher
Hercules, Inc.
P.O. Box 98
Magna, UT 84044

W. Waesche
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

Dr. R. Bernecker
Naval Surface Weapons Center
Code R13
White Oak
Silver Spring, MD 20910

Prof. Edward Price
Georgia Institute of Tech.
School of Aerospace Engineering
Atlanta, GA 30332

J.A. Birkett
Naval Ordnance Station
Code 5253K
Indian Head, MD 20640

Prof. R.W. Armstrong
University of Maryland
Dept. of Mechanical Engineering
College Park, MD 20742

Herb Richter
Code 385
Naval Weapons Center
China Lake, CA 93555

J.T. Rosenberg
SRI International
333 Ravenswood Ave.
Menlo Park, CA 94025

G.A. Zimmerman
Aeroject Tactical Systems
P.O. Box 13400
Sacramento, CA 95813

Prof. Kenneth Kuo
Pennsylvania State University
Dept. of Mechanical Engineering
University Park, PA 16802

T.L. Boggs
Naval Weapons Center
Code 3891
China Lake, CA 93555

(DYN)

DISTRIBUTION LIST

Dr. C.S. Coffey
Naval Surface Weapons Center
Code R13
White Oak
Silver Spring, MD 20910

D. Curran
SRI International
333 Ravenswood Avenue
Menlo Park, CA 94025

E.L. Throckmorton
Code SP-2731
Strategic Systems Program Office
Crystal Mall #3, RM 1048
Washington, DC 23076

Dr. R. Martinson
Lockheed Missiles and Space Co.
Research and Development
3251 Hanover Street
Palo Alto, CA 94304

C. Gotzmer
Naval Surface Weapons Center
Code R-11
White Oak
Silver Spring, MD 20910

G.A. Lo
3251 Hanover Street
B204 Lockheed Palo Alto Research Lab
Palo Alto, CA 94304

R.A. Schapery
Civil Engineering Department
Texas A&M University
College Station, TX 77843

J.M. Culver
Strategic Systems Projects Office
SSPO/SP-2731
Crystal Mall #3, RM 1048
Washington, DC 20376

Prof. G.D. Duvall
Washington State University
Department of Physics
Pullman, WA 99163

Dr. E. Martin
Naval Weapons Center
Code 3858
China Lake, CA 93555

Dr. M. Farber
135 W. Maple Avenue
Monrovia, CA 91016

W.L. Elban
Naval Surface Weapons Center
White Oak, Bldg. 343
Silver Spring, MD 20910

G.E. Manser
Morton Thiokol
Wasatch Division
P.O. Box 524
Brigham City, UT 84302

R.G. Rosemeier
Brimrose Corporation
7720 Belair Road
Baltimore, MD 20742

Administrative Contracting
Officer (see contract for
address)
(1 copy)

Director
Naval Research Laboratory
Attn: Code 2627
Washington, DC 20375
(6 copies)

Defense Technical Information Center
Bldg. 5, Cameron Station
Alexandria, VA 22314
(12 copies)

Dr. Robert Polvani
National Bureau of Standards
Metallurgy Division
Washington, D.C. 20234

Dr. Y. Gupta
Washington State University
Department of Physics
Pullman, WA 99163

END
FILMED

5-86

DTIC