

AD-A166 669


SCANNING ELECTRON MICROSCOPE STUDY OF NITROGUANIDINE
M31A1 AND M30 PROPELLANTS(U) ARMY ARMAMENT RESEARCH AND
DEVELOPMENT CENTER DOVER NJ ARMA. . 5 MORROW APR 86
ARAED-TR-86011


1/1

UNCLASSIFIED

F/G 19/1

NL

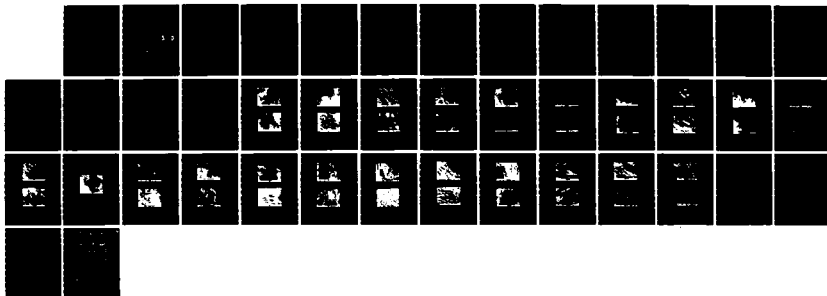

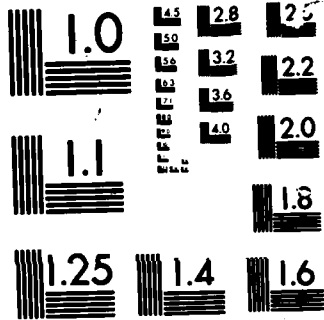

MICROCOPY

CHART

12

AD-A166 669

AD

AD E401 485

TECHNICAL REPORT ARAED-TR-86011

SCANNING ELECTRON MICROSCOPE STUDY OF
NITROGUANIDINE, M31A1, AND M30 PROPELLANTS

SCOTT MORROW

DTIC
ELECTE
APR 09 1986
S D
D

APRIL 1986



US ARMY
ARMAMENT
MUNITIONS &
CHEMICAL COMMAND
ARMAMENT R&D CENTER

U. S. ARMY ARMAMENT RESEARCH AND DEVELOPMENT CENTER

ARMAMENT ENGINEERING DIRECTORATE

DOVER, NEW JERSEY

APPROVED FOR PUBLIC RELEASE: DISTRIBUTION IS UNLIMITED.

DTIC FILE COPY

86

010

The views, opinions, and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy, or decision, unless so designated by other documentation.

The citation in this report of the names of commercial firms or commercially available products or services does not constitute official endorsement by or approval of the U.S. Government.

Destroy this report when no longer needed. Do not return to the originator.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report ARAED-TR-86011	2. GOVT ACCESSION NO. AD-A166669	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) SCANNING ELECTRON MICROSCOPE STUDY OF NITROGUANIDINE, M31A1, AND M30 PROPELLANTS		5. TYPE OF REPORT & PERIOD COVERED
7. AUTHOR(s) Scott Morrow		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS ARDC, AED Energetics & Warheads Division [SMCAR-AEE] Dover, NJ 07801-5001		8. CONTRACT OR GRANT NUMBER(s)
11. CONTROLLING OFFICE NAME AND ADDRESS ARDC, IMD STINFO Div [SMCAR-MSI] Dover, NJ 07801-5001		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 1A-3-8423
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE April 1986
		13. NUMBER OF PAGES 42
		15. SECURITY CLASS. (of this report) Unclassified
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution is unlimited.		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES This project was initiated in 1984 by the Large Caliber Weapon Systems Laboratory, Energetic Materials Division, ARDC.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Triple base propellants Scanning electron microscopy of propellants Particle size of nitroguanidine in triple base Nitroguanidine particle size		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Scanning electron photomicrographs were made of a reference sample of nitroguanidine (NQ) obtained from a Canadian manufacturer who has suspended production. Similar photos of nitroguanidine made at the Sunflower Army Ammunition Plant (SFAAP) and at the U.S. Army Armament Research and Development Center (ARDC) were compared to the Canadian reference material.		

(continued)

UNCLASSIFIED

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

20. ABSTRACT (continued)

From these photomicrographs the range of crystal sizes in the different samples was estimated. These NQ samples were incorporated into M31A1 and M30 propellants. Scanning electron microscope (SEM) photomicrographs of the resultant propellants revealed the long NQ needles break up during processing and that particle size differences in the original NQ are also seen in the same order in finished products.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

B

CONTENTS

	Page
Introduction	1
Experimental	1
Results and Discussion	1
Evaluation of NQ Samples	1
Evaluation of Various NQ's in M31A1 and M30 Propellants	3
Conclusions	4
Recommendations	5
Distribution List	33

Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification
By	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A1	



TABLES

	Page
1 Crystalline nitroguanidine	7
2 M31A1 propellant	8
3 M30 propellant	9

FIGURES

		Page
1	Canadian 6 μm CCL-9-418 nitroguanidine	11
2	Sunflower 4 μm SOW 83 H001-004	11
3	Canadian 6 μm CCL-9-418	12
4	Sunflower 4 μm SOW 83H 001-004	12
5	Sunflower 4 μm SOW 83H 001-004	13
6	Sunflower 4 μm SOW 83H 001-004 at higher magnification than in figure 5	13
7	Sunflower 6 μm SOW 83G 001-002	14
8	Sunflower 4 μm SOW 83H 001-004	14
9	Sunflower 10 μm SOW 83H 001-003	15
10	Sunflower 6 μm SOW 83G 001-002	15
11	Sunflower 10 μm SOW 83H 001-003	16
12	ARDC LCP-A-6814 Batch 1	16
13	ARDC LCP-A-6814 Batch 1 at higher magnification than in figure 12	17
14	ARDC LCP-A-6814 Batch 2 at even higher magnification than figures 12 and 13	17
15	ARDC LCP-A-6814 Batch 2	18
16	ARDC LCP-A-6814 Batch 2 at higher magnification than in figure 15	18
17	ARDC LCP-A-6814 Batch 2 at even higher magnification than in figure 16	19
18	ARDC LCP-A-6814 Batch 2 at same magnification as in figure 17	19
19	Special nitroguanidine	20
20	Special nitroguanidine at increased magnification than in figure 19	20

	Page
21 Special nitroguanidine at even higher magnification than in figure 20	21
22 Special nitroguanidine at even higher magnification than in figure 21	21
23 Special nitroguanidine at the highest magnification in the series of figures 19 through 23	22
24 M31A1 4 μ m RAD 84 B 000 E 148	23
25 M31A1 6 μ m RAD 84 B 000 E 146 in a different view from figure 24	23
26 M31A1 6 μ m RAD 84 B 000 E 147 in another different view than those in figures 24 through 26	24
27 M31A1 10 μ m RAD 84 B 000 E 151 in a view different from that in figure 32	24
28 M31A1 4 μ m RAD 84 B 000 E 148	25
29 M31A1 6 μ m RAD 84 B 000 E 146	25
30 M31A1 6 μ m RAD 84 B 000 E 147	26
31 M31A1 10 μ m RAD 84 B 000 E 151	26
32 M31A1 CCL 6 μ m RAD 80 M 07 00 77	27
33 M31A1 CCL 6 μ m RAD 80 M 07 00 77 in a view different from that in figure 32	27
34 M31A1 CCL 6 μ m RAD 80 M 07 00 77 showing the fractured surface	28
35 M31A1 CCL 6 μ m RAD 80 M 07 00 77 showing the surface of the burning rate hole longitudinally from left to right	28
36 M30 CCL 6 μ m RAD 78 K 06 99 03	29
37 M30 6 μ m RAD C 000 E 137	29
38 M30 6 μ m RAD C 000 E 138	30
39 M30 4 μ m RAD 84 C 000 E 139	30
40 M30 10 μ m RAD 84 C 000 E 143	31
41 M30 ppt. RAD C 000 E 145	31
42 M30 CCL 6 μ m RAD 78K 06 99 03	32
43 M30 4 μ m RAD C 000 E 139	32

INTRODUCTION

Canadian nitroquanidine (NQ) used in triple base propellant ceased to be manufactured in 1978. In order to provide a replacement for this critical material, manufacture was initiated at the Sunflower Army Ammunition Plant (SFAAP). A critical part of the process is control of particle size. A difficult problem in this regard is the on-stream measurement of the particle size. Nor is it a trivial matter to measure the particle size of the end product. Comprehensive studies have been made of the best means for making both types of particle size measurements. The Fisher Sub Sieve Sizer (FSSS) is the current specification method used to measure the dry product. Many other methods have been investigated, too. Although classical particle size measurements with the microscope are tedious as compared to other automated instrumental techniques, they still are the most accurate ones.

Hence, a scanning electron microscope (SEM) study was undertaken to get an accurate assessment of the particle size of both the old Canadian product as reference and different batches of product from the SFAAP as well as several experimental ones made at the U.S. Army Armament Research and Development Center (ARDC). This report is concerned with the findings of this study.

EXPERIMENTAL

Canadian, Sunflower Army Ammunition Plant (SFAAP), and experimental batches of NQ were examined. The latter types had been prepared in small lots of up to 200 pounds each at this installation. An AMRAY VTC 1400 SEM was used to photograph the samples; Dow Polystyrene Latex spheres with a diameter of 0.264 μm were used to calibrate the SEM's magnification scale. Polaron Instruments Microstick 1214 was used to mount samples on aluminum stubs for plating with Pd/Au prior to introduction into the SEM.

RESULTS AND DISCUSSION

Evaluation of NQ Samples

Measurements of the dimensions of crystals from SEM photomicrographs are recorded in table 1. The discontinued Canadian product, sample 1, CCL-9-418, is more uniform in particle size than the other samples. The two most uniform batches of American manufacture are sample 2, Sunflower SOW 83 H001-004, and sample 3, SOW 83 G001-002. cursory inspection of photos at the same magnifications, figures 1 versus 2 and 3 versus 4 confirms that the crystals in the Canadian sample designated as 6 μm size are, on the whole, larger than those in the Sunflower sample designated as 4 μm size, SOW 83 H001-004. Thus SEM observations are in accord with previous relative (but not necessarily absolute) particle size designations arrived at by FSSS analysis. The white bar in the middle

of the legend at the bottom of the picture is a measurement reference labeled in μm . In the case of figures 1 and 2 the bar represents 100 μm ("U" in the legend). Although the Canadian sample contains smaller crystals which are about 10 μm in length and 0.25-0.5 μm wide, it is essentially free from "fines." The bulk of the needles are 30 to 150 μm in length and 5 to 15 μm wide. No distinction is made between width and thickness of the particles since, in most cases, only one side is seen in the photos. There may well be a tendency, at least in the case of the larger needles, for them to be more broad than thick.

The SOW 83H 001-004 NQ designated as 4 μm in size consists, for the most part, of fairly well-formed needles. However, some are fused together in bundles. Lengths of the needles vary from about 10 to 100 μm with a few being even longer. The bulk of them are nearer to being 100 μm long, with a relatively small amount of fines being present. The smaller needles tend to be about 0.25 μm in width and thickness whereas the larger ones are nearer 0.5 to 1.5 μm . Thickness and widths are nearly equal, though there may be a tendency for them to be somewhat more broad than thick. Appearance of the samples indicates that the crystallization process was well-controlled, giving a reasonably uniform product. Photomicrographs taken at higher magnifications are shown in figures 5 and 6.

The nominally 6 μm NQ, SOW 83G 001-002, contains noticeably larger sized needles than the 4 μm sample (figure 7 versus 8). The amount of fines in this 6 μm sample is moderate. The needles here are well-formed too, and sufficiently physically uniform to indicate the crystallization process was well-controlled. The fines consist of rods about 5 to 20 μm long and about 0.25 μm in width. The larger ones are up to about 300 μm in length and 2.5 to 10 μm in thickness and width. Again it appears that some of the larger crystals are wider than they are thick. There is a greater variation in the size of particles and incidence of larger ones in this sample than in the reference 6 μm Canadian one, CCL-9-418. By inference, the crystallization process was not as precisely controlled as the Canadian one.

The sample of NQ, SOW 83H 001-003, classed as 10 μm size contains significant numbers of needles that are larger than those in the preceding 6 μm sample (figure 9 versus 10). In this case, too, the appearance of the crystals indicates the process used to form them was relatively well controlled. However, the difference in size between the fines and large crystals is greater than in the case of the aforementioned 4 and 6 μm samples. The "fines" are rods ranging in length up to 50 μm . They are about 0.25-0.5 μm wide and probably of nearly equal thickness. The larger ones are as long as 1500 μm , in some cases, but more often 150 to 500 μm . They vary in width from about 10 to 20 μm . Though many appear to be of similar width and thickness, there are some that seem to be more broad than thick. Figure 11 shows the appearance of these nominally 10 μm crystals at a higher magnification.

The sample of NQ from ARDC, number 5, table 1, designated as LCP-A-6814, batch 1, is quite different in particle size and shape than the reference batch from Canada and the three from SFAAP. The latter four Canadian and Sunflower samples are nominally designated as being 4 to 10 μm in particle size. Considerably higher magnifications were required to characterize these ARDC samples with high concentrations of ultrafine particle size crystals. Magnifications 10 to 50

times greater than those used with the Canadian and Sunflower samples were required to bring out the details of the ultrafine particles (figures 12 and 13). Even the smallest crystals in ARDC Sample 5, table 1, LCP-A-6814) show good development. They tend to be more rectangular or hexagonal in shape as the case may be, and less needle-like than those in the Canadian and SFAAP samples. Their striking features are that they are wider and thicker with respect to length than the others. Also there is quite a disparity in sizes. Most of them are very small, but well developed, being in some cases less than $0.5 \mu\text{m}$ long and about $0.25 \mu\text{m}$ thick to about $10 \mu\text{m}$ long and $2 \mu\text{m}$ thick. The larger ones are up to $170 \mu\text{m}$ long and $20 \mu\text{m}$ thick. Good crystal development in both small and large crystals shows the process was well-controlled, in spite of the size difference.

The other sample made at ARDC, number 6, table 1, LCAP 6814, batch 2, was similar to sample 5, batch 1. It too was notable not only in superior crystal development but also in the difference between the sizes and morphology of the large and small crystals. The huge difference in sizes between the small and large crystals can be seen in figures 14 through 18. The small ones were as short as $0.5 \mu\text{m}$ in length and $0.25 \mu\text{m}$ wide. Most were at least $2 \mu\text{m}$ long and $0.5 \mu\text{m}$ wide. The large ones ranged from about 50 to $200 \mu\text{m}$ in length and were 10 to $20 \mu\text{m}$ wide. Width and thicknesses seemed to be similar.

Sample 7, table 1, which was a special ARDC laboratory prepared NQ, was somewhat different from all the other samples. However, it resembled the ARDC samples more closely than those from Canada and Sunflower. Like the ARDC samples it contained two types of crystals. The first were small, well-formed ones with widths varying from about 0.5 to $1.0 \mu\text{m}$ and lengths from 1 to $5 \mu\text{m}$. The second type of crystal was the bulkier, larger kind which was about 3 to $5 \mu\text{m}$ wide and 5 to $10 \mu\text{m}$ long. In addition there was a third kind of crystal, which was an elongated form of the smaller types of crystals. These were about 0.3 to $1 \mu\text{m}$ wide and 10 to $40 \mu\text{m}$ long. The crystals were well-formed. Figures 19 through 23 illustrate these details.

Evaluation of Various NQ's in M31A1 and M30 Propellants

It is understandably more difficult to obtain measurements of NQ crystal dimensions in a propellant than with the original NQ samples. A notable feature of the five lots of M31A1 propellants is the more uniform length of the larger NQ crystals in the propellant matrix than is the case with the neat NQ samples. This can be attributed to breakup of the longer needles to shorter lengths during the propellant mixing operation. Crystallinity of the samples of NQ remains good in the finished propellants. As can be seen from table 2, significant size differences seem to exist between the different samples with regard to NQ crystal size. It should be emphasized, however, that the extreme measurements of crystal sizes are made upon the relatively few crystals that can be observed more or less entirely in the photomicrographs. Although such measurements can be made accurately, in the absence of many more photos at suitable magnifications there is a substantial degree of uncertainty in assigning given values as being representative of the whole batch of propellant.

The appearance of the four M31A1 propellants made from SFAAP NQ with nominal particle sizes of 4 to 10 μm , 1 and 3-5, table 2, are seen in figures 24 through 27. The original magnification in this series of photographs before they were altered in size for publication was 500X. The bar in the middle of the legend of the pictures at the bottom, however, can be used as a reference for measurements in every case regardless of changes in picture size. Figures 28 through 31 show the same propellants at twice the magnification of the previous four photographs. In each of these series the nominal 4 μm size material in RAD 84B00E 148, sample 1, table 2, is smaller than that in the other three Sunflower propellants. It is difficult to find much difference in the overall appearance of the crystals in the other three samples 3, 4 and 5, table 2. Figures 32 through 35 represent the propellants made with nominally 6 μm Canadian NQ. A comparison of the propellants made from the SFAAP and from Canadian NQ indicates that crystals in the latter material are of exceptionally uniform, small particle size. Of all of the photographs presented here, figure 35 most clearly shows hollow NQ crystals. Hollow ones are marked with arrows. Some of the other crystals in the photograph that are not marked appear to be hollow, too.

Observations on the six M30 propellants are listed in table 3. Significant differences in NQ particle size and orientation in M30 propellants were detected. It was difficult, for the most part, to find crystals that were fully revealed in the propellant mass. The range of particle sizes listed in table 3 were made on the few that were accessible to measurement. The M30 propellants are shown in figures 36 through 41, which are at the same magnification and in the same serial order as in table 3. Although the fine particles in figure 41 of the propellant with ARDC precipitated NQ are difficult to distinguish at 200X, the larger particles show up clearly. The similarity in appearance of the M30 propellants made from nominal 6 μm Canadian and 4 μm Sunflower NQ is illustrated in figures 42 and 43.

CONCLUSIONS

Comparing the Canadian NQ to that made at SFAAP and ARDC, one finds that the Canadian material is unique in that it is exceptionally uniform in particle size and is relatively free of "fines." The particle size rankings of the NQ reported by SFAAP were confirmed by SEM.

It is obvious that the nominal particle sizes determined by other particle size measuring techniques do not reflect the actual sizes seen in the SEM photomicrographs.

A comparison of the three SFAAP NQ samples indicates that the 4 μm NQ is more uniform in crystal size than both the 6 μm and 10 μm sizes.

The ARDC samples, morphologically speaking, are substantially different from the Canadian and SFAAP NQ. There is a preponderance of ultrafine particle size material in the ARDC samples. The special laboratory prepared ARDC NQ has significant numbers of short thick crystals, very small in size, and the smallest particle size of all the NQ samples evaluated.

The results for the M31A1 and M30 formulations indicate that the NQ crystals in the propellants containing Canadian 6 μm and the Sunflower 4 μm NQ, respectively, appear to be smaller than the other NQ's. The most atypical propellant was the ARDC special sample wherein the finer particles were relatively indistinguishable at 200X, compared to the other samples. The SEM photographs of the M30 and M31A1 propellants revealed that the varied, long needled NQ's break-up during processing and are more uniform in length in the finished propellants.

RECOMMENDATIONS

It should be pointed out that wet samples suspended in liquids can be examined by appropriate types of electron microscopes or ones with special accessories. Thus, electron microscopes can be used to back-up on-stream measurements to get a quick assessment of the product without resorting to rigorous particle size measurements and counting procedures. The utility of the scanning electron microscope for sizing the final, dry product has been demonstrated and should be used as a reference standard to ensure the accuracy of other methods which are based on less direct measurements.

Table 1. Crystalline nitroguanidine

1	2	3 ^a	4 ^b	5	6 ^b	7
Sample Source	Designation	Nominal particle size μm , (uniformity of particle size)	Smaller particles width \times length, μm	Ratio of length to width of larger ones in column 4	Larger particles width \times length, μm	Ratio of length to width of larger ones in column 6
1	Canada CCL-9-418	6 (good)	0.25-0.5 \times 10	20:1	5-15 \times 30-150	10:1
2	US SFAAP SOW 83 H001-004	4 (fair)	0.25 \times 10	40:1	0.5-1.5 \times 1000	67:1
3	US SFAAP SOW 83 G001-002	6 (fair)	0.25 \times 5-20	4:1	2.5-10 \times 300	30:1
4	US SFAAP SOW 83 H001-003	10 (poor)	0.25 \times 0.5-50	100:1	10-20 \times 1500	75:1
5	ARDC LCP-A-6814 Batch 1	- (poor)	0.25-2 \times 0.5 - 10	5:1	20 \times 170	8.5:1
6	ARDC LCP-A-6814 Batch 2	- (poor)	0.25-1 \times 0.5 - 6	6:1	10-20 \times 50-200	10:1
7	ARDC Special	- (poor)	0.5-1.0 \times 1-5; 0.3-1.0 \times 10-40	5:1 40:1	3-5 \times 5 - 10	2:1

^aThis is the size reported from standard analysis by FSSS.

^bThese measurements were made from SEM photomicrographs.

Table 2. M31A1 propellant

<u>Number</u>	<u>Source</u>	<u>Designation</u>	<u>Nominal size Nitroguanidine μm</u>	<u>Smaller par- ticles, width \times length, μm</u>	<u>Larger par- ticles width \times length, μm</u>	<u>Remarks</u>
1	Sunflower	RAD 84B 000E 148	4	0.5-1 \times 2-5	3-10 \times 10-60	Preponderance of larger, parallel oriented xtals
2	Canadian JCL	RAD 80M 070077	6	2 \times 5-10	1.5-10 \times 10-40	Crystals seem to be more randomly oriented than in 3 and 4
3	Sunflower	RAD 84B 000E 146	6	2 \times 2-20	10-15 \times 60 - 100	Preponderance of larger, parallel oriented crystals
4	Sunflower (Macaroni pressed)	RAD 84B 000E 147	6	1 \times 5-15	2-15 \times 20-100	Preponderance of larger crystals, some random orientation
5	Sunflower	RAD 84B 000E 151	10	0.5-1 \times 2-5	4-10 \times 30-70	Some random orien- ting of crystals as in 2, prepon- derance of larger crystals

Table 3. M30 propellants

<u>Number</u>	<u>Source</u>	<u>Designation</u>	<u>Nominal size nitro-guanidine, μm</u>	<u>Estimated range of particle sizes, width x length, μm</u>	<u>Remarks</u>
1	CCL	RAD78K069903	6	10-90	Crystals fairly uniform in size, nearly parallel
2	SFAAP	RADC000E137	6	(5-16) x (58-126)	Crystals fairly uniform in size, nearly parallel
3	SFAAP	RADC000E138	6	(8-21) x (63-100)	Crystals fairly uniform with some oversized ones, nearly parallel
4	SFAAP	RADC000E139	4	(2-12) x (up to 20)	High magnification photo at 2000 X shows wide variance in crystal size, nearly parallel
5	SFAAP	RAD84C000E143	10	(8-21) x (37-2632)	Wide variation in particle size, nearly parallel
6	ARDC	RADC000E145	ppt.	(0.5-38) x (1.5-232)	Wide variation in particle size, random orientation

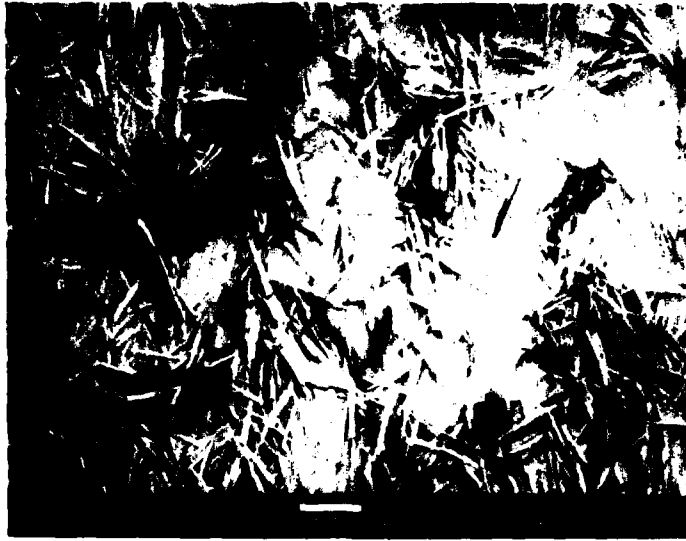


Figure 1. Canadian 6 μm CCL-9-418 nitroguanidine

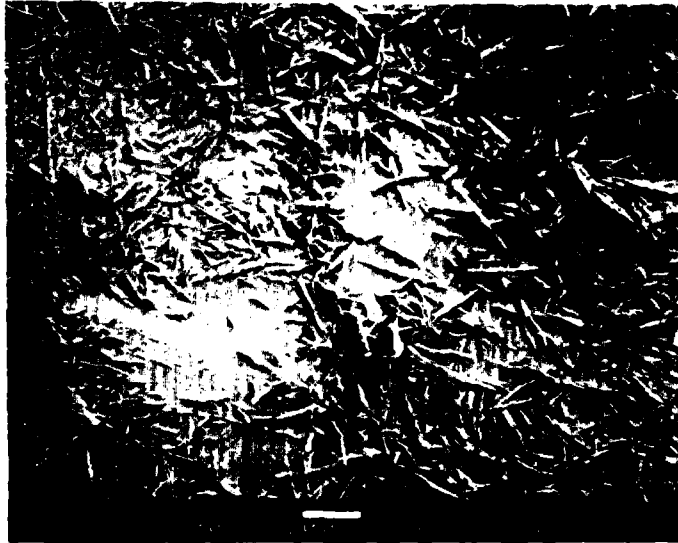


Figure 2. Sunflower 4 μm SOW 83 H001-004



Figure 3. Canadian 6 μm CCL-9-418

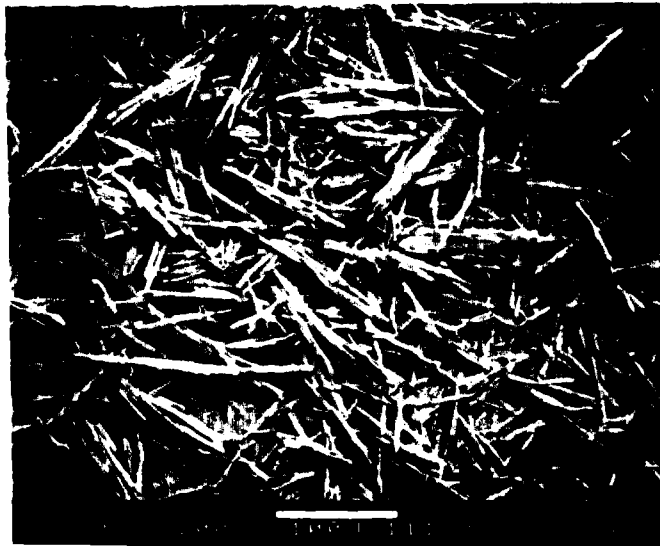


Figure 4. Sunflower 4 μm SOW 83H 001-004



Figure 5. Sunflower 4 μm SOW 83H 001-004



Figure 6. Sunflower 4 μm SOW 83H 001-004 at higher magnification than in figure 5



Figure 7. Sunflower 6 μm SOW 83G 001-002



Figure 8. Sunflower 4 μm SOW 83H 001-004



Figure 9. Sunflower 10 μm SOW 83H 001-003

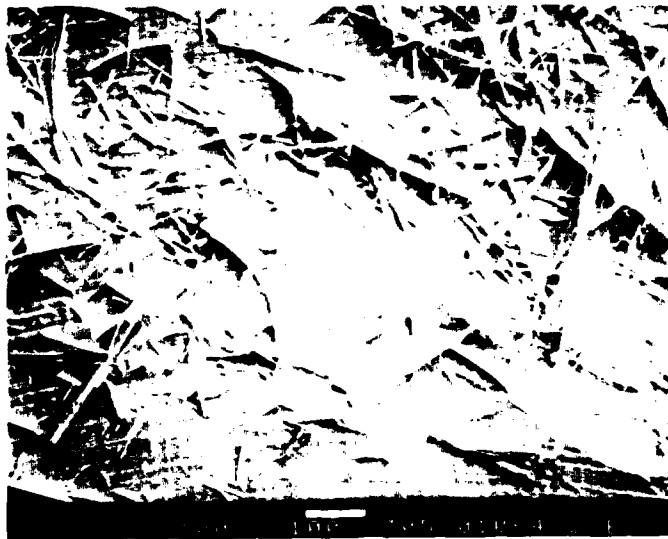


Figure 10. Sunflower 6 μm SOW 83G 001-002



Figure 11. Sunflower 10 μm SOW 83H 001-003

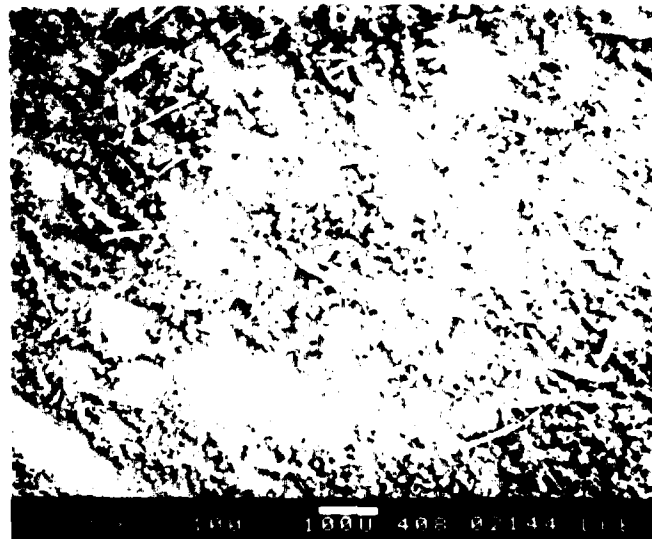


Figure 12. ARDC LCP-A-6814 Batch 1



Figure 13. ARDC LCP-A-6814 Batch 1 at higher magnification than in figure 12



Figure 14. ARDC LCP-A-6814 Batch 2 at even higher magnification than figures 12 and 13

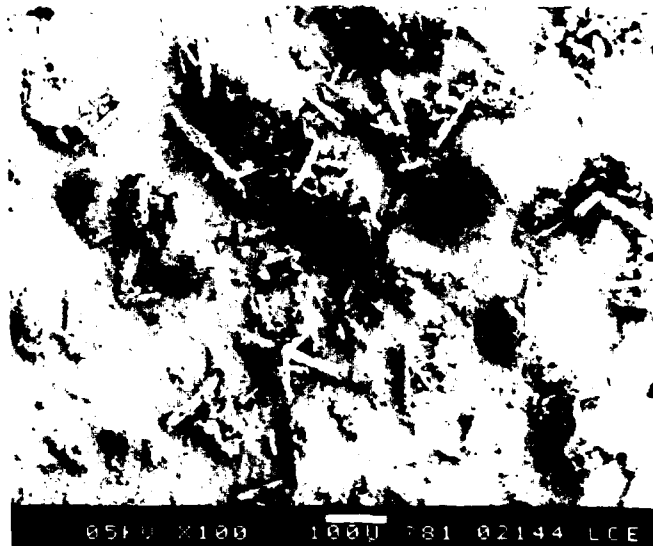


Figure 15. ARDC LCP-A-6814 Batch 2

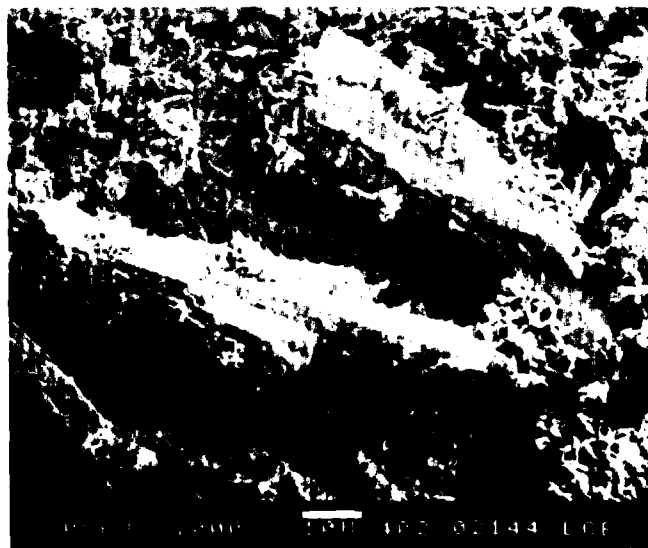


Figure 16. ARDC LCP-A-6814 Batch 2 at higher magnification than in figure 15

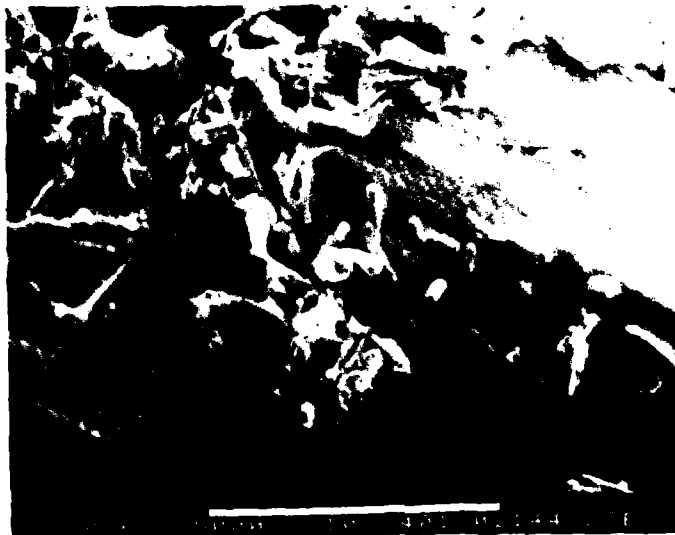


Figure 17. ARDC LCP-A-6814 Batch 2 at even higher magnification than in figure 16

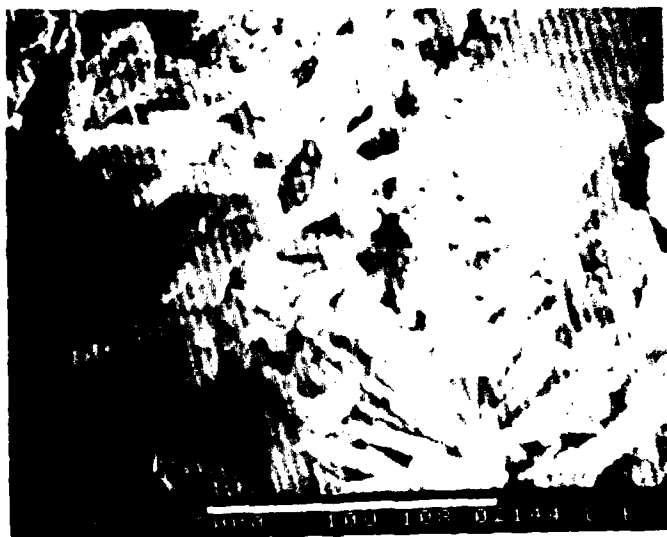


Figure 18. ARDC LCP-A-6814 Batch 2 at same magnification as in figure 17

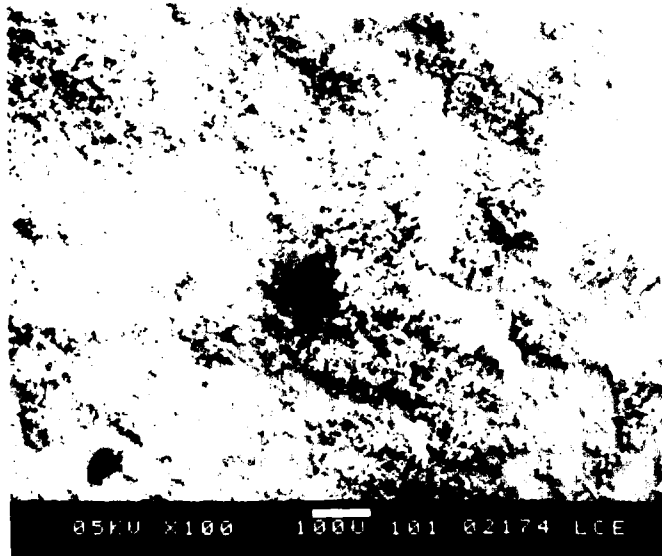


Figure 19. Special nitroguanidine

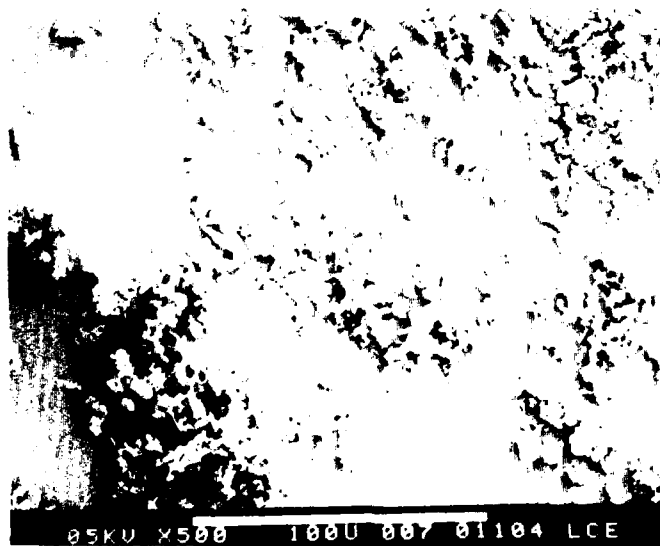


Figure 20. Special nitroguanidine at increased magnification than in figure 19

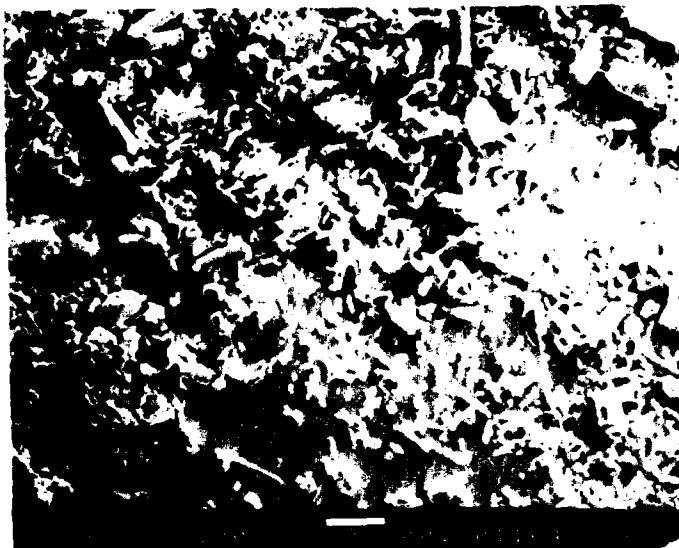


Figure 21. Special nitroguanidine at even higher magnification than in figure 20



Figure 22. Special nitroguanidine at even higher magnification than in figure 21

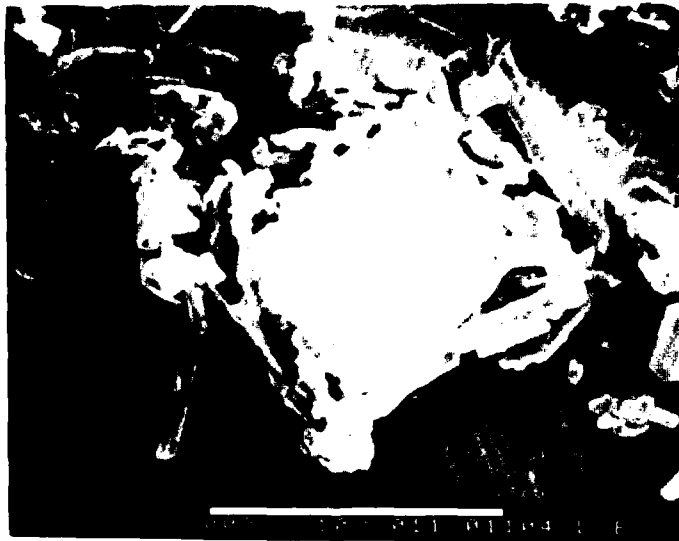


Figure 23. Special nitroguanidine at the highest magnification in the series of figures 19 through 23

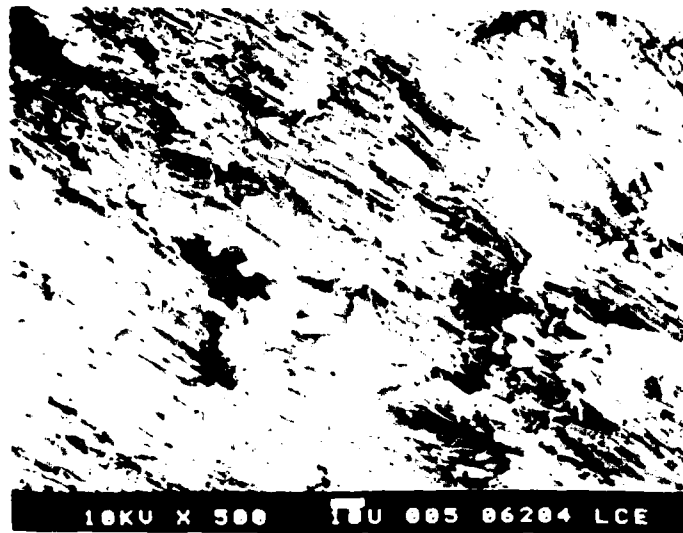


Figure 24. M31A1 4 μm RAD 84 B 000 E 148

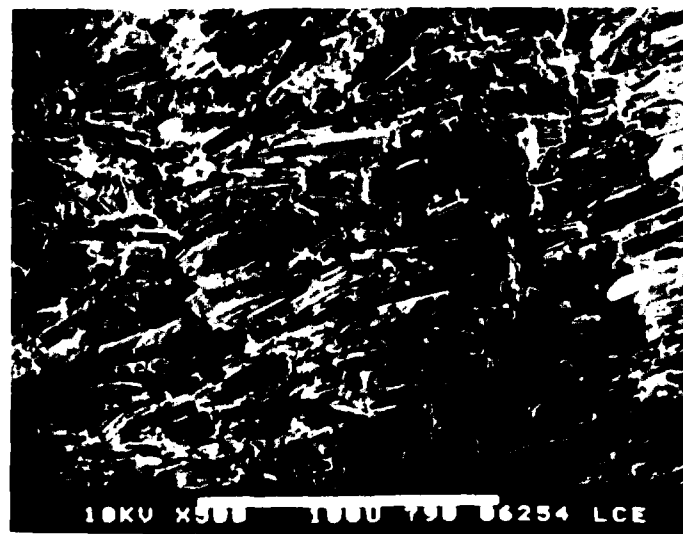


Figure 25. M31A1 6 μm RAD 84 B 000 E 146 in a different view from figure 24

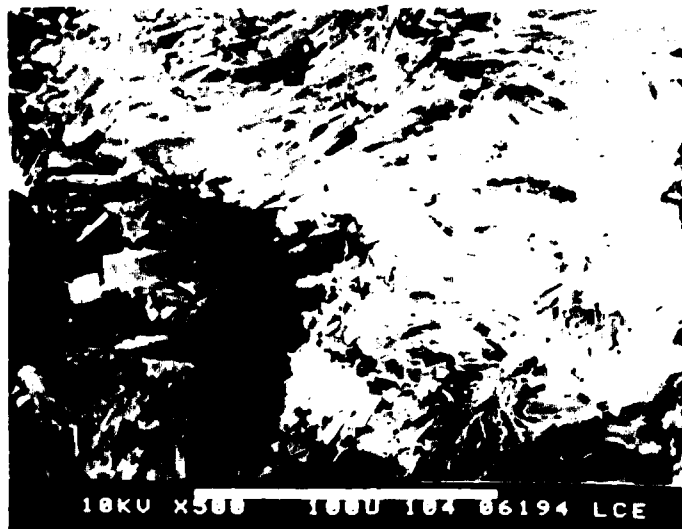


Figure 26. M31Al 6 μm RAD 84 B 000 E 147 in another different view than those in figures 24 through 26

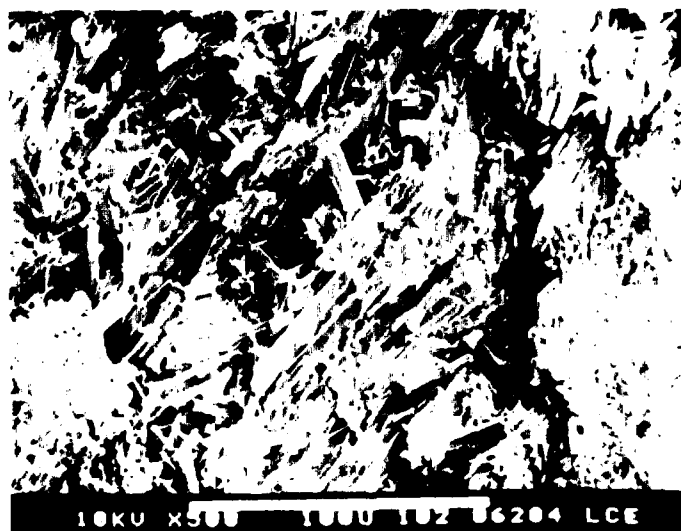


Figure 27. M31Al 10 μm RAD 84 B 000 E 151 in a view different from that in figure 32

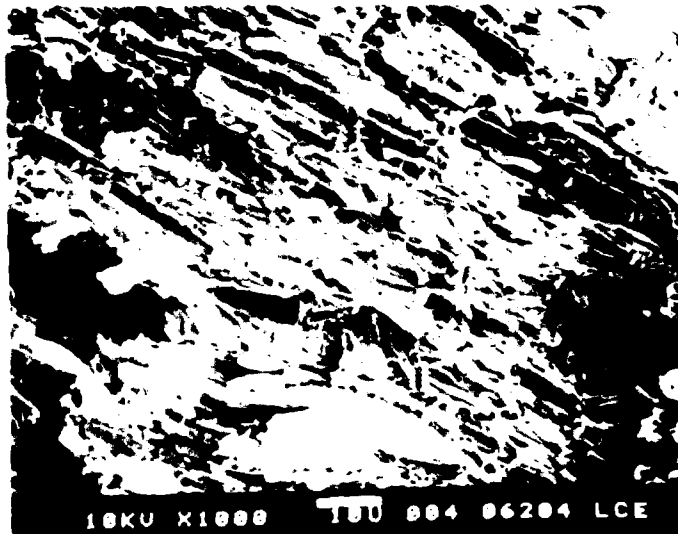


Figure 28. M31A1 4 μ m RAD 84 B 000 E 148



Figure 29. M31A1 6 μ m RAD 84 B 000 E 146



Figure 30. M31A1 6 μ m RAD 84 B 000 E 147



Figure 31. M31A1 10 μ m RAD 84 B 000 E 151



Figure 32. M31A1 CCL 6 μm RAD 80 M 07 00 77



Figure 33. M31A1 CCL 6 μm RAD 80 M 07 00 77 in a view different from that in figure 32



Figure 34. M31A1 CCL 6 μm RAD 80 M 07 00 77 showing the fractured surface



Figure 35. M31A1 CCL 6 μm RAD 80 M 07 00 77 showing the surface of the burning rate hole longitudinally from left to right



Figure 36. M30 CCL 6 μ m RAD 78 K 06 99 03



Figure 37. M30 6 μ m RAD C 000 E 137

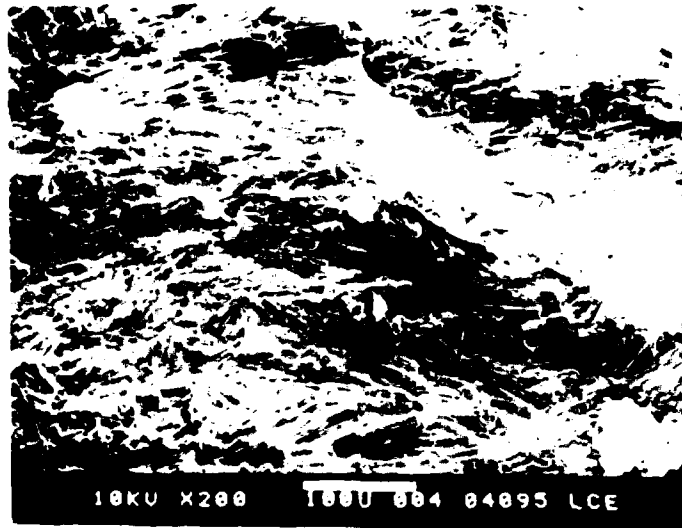


Figure 38. M30 6 μm RAD C 000 E 138



Figure 39. M30 4 μm RAD 84 C 000 E 139

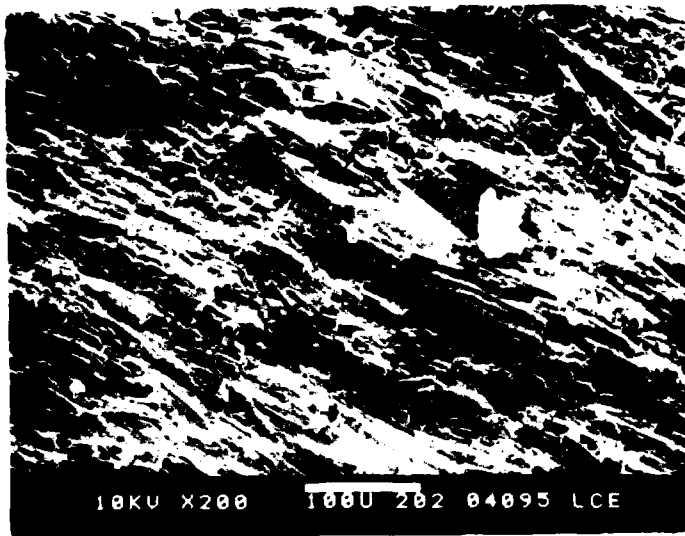


Figure 40. M30 10 μ m RAD 84 C 000 E 143



Figure 41. M30 ppt. RAD C 000 E 145

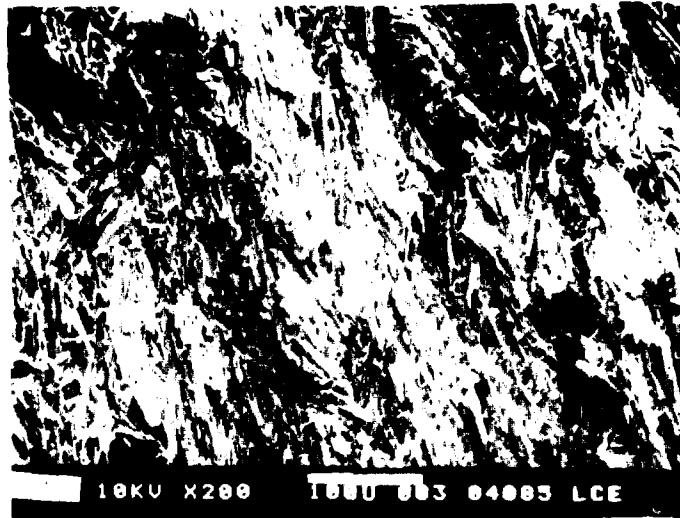


Figure 42. M30 CCL 6 μm RAD 78K 06 99 03



Figure 43. M30 4 μm RAD C 000 E 139

DISTRIBUTION LIST

Commander
Armament Research and Development Center
U.S. Army Armament, Munitions and Chemical Command
ATTN: SMCAR-AE, G. Taylor
SMCAR-AEE, Word Processing Office (3)
SMCAR-AEE-BP, D. Downs
A. Beardell
SMCAR-MSI (5)
SMCAR-TD
SMCAR-TDC
Dover, NJ 07801-5001

Commander
U.S. Army Armament, Munitions and Chemical Command
ATTN: AMSMC-GCL(D)
Dover, NJ 07801-5001

Administrator
Defense Technical Information Center
ATTN: Accessions Division (12)
Cameron Station
Alexandria, VA 22304-6145

Director
U.S. Army Materiel Systems Analysis Activity
ATTN: AMXSY-MP
Aberdeen Proving Ground, MD 21005-5066

Commander
Chemical Research and Development Center
U.S. Army Armament, Munitions and Chemical Command
ATTN: SMCCR-SPS-IL
Aberdeen Proving Ground, MD 21010-5423

Commander
Chemical Research and Development Center
U.S. Army Armament, Munitions and Chemical Command
ATTN: SMCCR-RSP-A
Aberdeen Proving Ground, MD 21010-5423

Director
Ballistic Research Laboratory
ATTN: AMXBR-OD-ST
Aberdeen Proving Ground, MD 21005-5066

Chief
Benet Weapons Laboratory, CCAC
Armament Research and Development Center
U.S. Army Armament, Munition and Chemical Command
ATTN: SMCAR-CCB-TL
Watervliet, NY 12189-5000

Commander
U.S. Army Armament, Munitions and Chemical Command
ATTN: SMCAR-ESP-L
Rock Island, IL 61299-6000

Director
U.S. Army TRADOC Systems Analysis Activity
ATTN: ATAA-SL
White Sands Missile Range, NM 88002

Commander
US Army Materiel Command
ATTN: AMCPM-GCM-WF
5001 Eisenhower Avenue
Alexandria, VA 22333-0001

Commander
US Army Materiel Command
ATTN: AMCDRA-ST
5001 Eisenhower Avenue
Alexandria, VA 22333-0001

Commander
US Army Materiel Command
ATTN: AMCLD, R. Vitali
I. Bartky
5001 Eisenhower Avenue
Alexandria, VA 22333-0001

HQDA
ATTN: DAMA-ART-M
DAMA-CSM
DAMA-ZA
Washington, DC 20310

Project Manager
Tank Main Armament Systems
ATTN: AMCPM-TMA, K. Russell - 120
AMCPM-TMA-105
AMCPM-TMA-120
Dover, NJ 07801-5001

Dr. Louis M. Cameron
Director, Army Research and Technology
Room 3E426
The Pentagon
Washington, DC 20310

END
FILMED

5-86

DTIC