

AD-A170 648

DISPLACEMENT FIELDS FOR MIXED MODE ELASTIC PLASTIC
CRACKS(U) MASSACHUSETTS INST OF TECH CAMBRIDGE DEPT OF
MECHANICAL ENGINEERING G A KARDONATEAS 31 JUL 86

1/1


UNCLASSIFIED

N00014-82-K-0025

F/G 20/11

NL



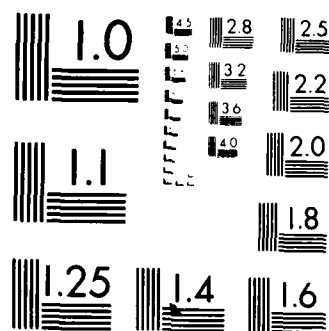

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS 1963-A

Technical Report N00014-82-K-0025 P00002 TR05

DISPLACEMENT FIELDS FOR MIXED MODE ELASTIC PLASTIC CRACKS

George A. Kardomateas


Room 1-304, (617) 253-2219

Department of Mechanical Engineering

Massachusetts Institute of Technology

Cambridge, MA 02139

AD-A170 648

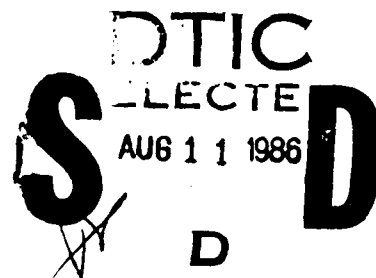

Unlimited Distribution

31 July, 1986

Technical Report

DISTRIBUTION STATEMENT A

Approved for public release
Distribution Unlimited

Prepared for

OFFICE OF NAVAL RESEARCH

Solids Mechanics Program, Mechanics Division

Scientific Officer: Dr. Yapa Rajapakse

Code 432S (202) 696-4306

800 N. Quincy Street

Arlington, VA 22217

DTIC FILE COPY

56 6 223

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER N00014-82-K-0025 P00002 TR05	2. GOVT ACCESSION NO. AD-A170648	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) DISPLACEMENT FIELDS FOR MIXED MODE ELASTIC PLASTIC CRACKS	5. TYPE OF REPORT & PERIOD COVERED Technical Report 31 July 1986	
7. AUTHOR(s) George A. Kardomateas (now at General Motors Research Lab, Engineering Mechanics Dept, Warren MI 48090-9055)		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Mechanical Engineering Massachusetts Institute of Technology Cambridge MA 02139		8. CONTRACT OR GRANT NUMBER(s) N00014-82-K-0025 P00002
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Solic Mechanics Program, Mech. Div, Code 432S 800 N. Quincy Street, Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE 31 July 1986
		13. NUMBER OF PAGES
		15. SECURITY CLASS. (of this report) Unclassified
		16. DECLASSIFICATION/DOWNGRADING SCHEDULE
18. DISTRIBUTION STATEMENT (of this Report) Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
19. SUPPLEMENTARY NOTES Submitted to J. Eng. Fract. Mech.		
21. KEY WORDS (Continue on reverse side if necessary and identify by block number) Mixed mode, Mode I, Mode II, theory, strain hardening, crack tip displacement, J-integral		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The displacement fields for deformation theory, power law plasticity are found from the Shih strain fields for the mixed mode case. These are needed to extend the McClintock and Slocum model to the more realistic case where the shear band is of finite width and the crack progresses to the tensile side of the shear band. The displacement fields should be useful in many other applications as well.		

DISPLACEMENT FIELDS FOR MIXED MODE ELASTIC PLASTIC CRACKS

G.A. KARDOMATEAS*

Massachusetts Institute of Technology
Cambridge, MA 02139

Shih [1] extended the HRR [2,3] singularity by giving the dominant singularity solutions governing the asymptotic stress and strain field of a stationary crack for the mixed Mode I and II case. In terms of a stress-strain law of the form $\sigma = \sigma_1 \epsilon^n$, with Mode I mixity parameter M^P , a far-field path independent integral J and the scalar function $I_{1/n}(M^P)$, the displacement and strain components at r, θ can be written [4]:

$$\frac{u_i(r, \theta)}{r} = \left[\frac{J}{\sigma_1 I_{1/n}(M^P) r} \right]^{1/(n+1)} \bar{u}_i(\theta, 1/n, M^P) . \quad (1)$$

$$\epsilon_{ij}(r, \theta) = \left[\frac{J}{\sigma_1 I_{1/n}(M^P) r} \right]^{1/(n+1)} \bar{\epsilon}_{ij}(\theta, 1/n, M^P) . \quad (2)$$

The displacement functions u_i are determined from the strain functions for the plane strain case considered here. The radial displacement u_r may be found from the radial strain,

$$\epsilon_{rr} = \frac{\partial u_r}{\partial r} , \quad (3)$$

so:

$$u_r = \int_0^r \epsilon_{rr} dr + u_r(0, \theta) . \quad (4)$$

For zero rigid-body translation at $r=0$, $u_r(0, \theta)=0$. Eliminating ϵ_{rr} with (2) and integrating (4) gives

*Present address: General Motors Research Laboratories, Engineering Mechanics
Department, RMB-256, Warren, Michigan 48090-9055

$$\frac{u_r}{r} = \left[\frac{J}{\sigma_1 r l(n, M^p)} \right]^{1/(n+1)} \left(\frac{n+1}{n} \right) \bar{\epsilon}_{rr} . \quad (5)$$

Introducing the radial displacement from (1) gives the angular function for the radial displacement $\bar{u}_r$:

$$\bar{u}_r(\theta, M^p, n) = \left(\frac{n+1}{n} \right) \bar{\epsilon}_{rr}(\theta, M^p, n) . \quad (6)$$

The tangential displacement u_θ is found by integrating the definition of $\epsilon_{\theta\theta}$,

$$\epsilon_{\theta\theta} = \frac{1}{r} u_r + \frac{1}{r} \frac{\partial u_\theta}{\partial \theta} , \quad (7)$$

to be

$$u_\theta = u_\theta(r, -\pi) + \int_{-\pi}^{\theta} (r \epsilon_{\theta\theta} - u_r) d\theta . \quad (8)$$

From (1), the θ -independent term $u_\theta(r, -\pi)$ must be $O(r^{n/(n+1)})$ and thus can be written in terms of a constant C :

$$u_\theta(r, -\pi) = \left[\frac{J}{\sigma_1 l(n, M^p)} \right]^{1/(n+1)} C r^{n/(n+1)} . \quad (9)$$

The integral of (8) can be converted to a single integral over $\bar{\epsilon}_{rr}(\theta)$ by noting $\epsilon_{\theta\theta} = -\epsilon_{rr}$ for incompressible plane strain, by using (2) for ϵ_{rr} , defining

$$F(\theta) = \int_{-\pi}^{\theta} \bar{\epsilon}_{rr} d\theta , \quad (10)$$

and introducing (5) for u_r :

$$u_\theta = \left[\frac{J}{\sigma_1 r l(n, M^p)} \right]^{1/(n+1)} r^{n/(n+1)} \left[C - \left(\frac{2n+1}{n} \right) F(\theta) \right] . \quad (11)$$

To determine the constant C , substitute (11) for u_θ and (5) for u_r in the definition of $\epsilon_{r\theta}$,

$$\epsilon_{r\theta} = \frac{1}{2} \left(\frac{\partial u_\theta}{\partial r} + \frac{1}{r} \frac{\partial u_r}{\partial \theta} - \frac{u_\theta}{r} \right) , \quad (12)$$

to get

$$C = \left(\frac{2n+1}{n}\right)F(\theta) + \frac{(n+1)^2}{n} \frac{\partial \bar{\epsilon}_{rr}}{\partial \theta} - 2(n+1)\bar{\epsilon}_{r\theta} . \quad (13)$$

Using (11) we can thus find the angular function for the tangential displacement, $\bar{u}_\theta$, in terms of the angular strain functions $\bar{\epsilon}_{rr}$ and $\bar{\epsilon}_{r\theta}$:

$$\bar{u}_\theta(\theta, M^p, n) = \frac{(n+1)^2}{n} \frac{\partial \bar{\epsilon}_{rr}}{\partial \theta} - 2(n+1)\bar{\epsilon}_{r\theta} . \quad (14)$$

Notice that the integral $F(\theta)$ does not enter into the expression for $\bar{u}_\theta$. Thus finally

$$\frac{u_\theta}{r} = \left[\frac{J}{\sigma_1 I(n, M^p)_r} \right]^{1/(n+1)} \left[\frac{(n+1)^2}{n} \frac{\partial \bar{\epsilon}_{rr}}{\partial \theta} - 2(n+1)\bar{\epsilon}_{r\theta} \right] . \quad (15)$$

Plots of the displacement functions, $\bar{u}$, determined numerically by (6), (14) from the strain functions given in [1] for two strain hardening exponents, $n=1/13$ and $n=1/3$, are shown in the figures. It was also verified that these equations give the strain functions (2), when substituted into the definitions (3), (7) and (12), and by using the compatibility equation which, in this case, reduces to

$$\frac{\partial^2 \bar{\epsilon}_{rr}}{\partial \theta^2} - \frac{n}{(n+1)^2} \bar{\epsilon}_{\theta\theta} + \frac{1}{n+1} \bar{\epsilon}_{rr} - \frac{2n}{n+1} \frac{\partial \bar{\epsilon}_{r\theta}}{\partial \theta} = 0 . \quad (16)$$

Acknowledgement - The financial support of the Office of Naval Research, Arlington, Virginia, Contract N0014-82K-0025 is gratefully acknowledged. The author is also grateful to Professor Frank McClintock for valuable discussions.

REFERENCES

1. Shih, C.F., Small scale yielding analysis of mixed mode plane strain crack problems. *Fracture Analysis, ASTM STP 560*, Am. soc. Test. Mat., Philadelphia, 187-210 (1974).
2. Hutchinson J.W., Singular Behavior at the end of a Tensile Crack in a Hardening Material. *J. Mech. Phys. Sol.*, 16, 13-31 (1968).



A-1

made and/or special

3. Rice J.R. and Rosengren G.F., Plane Strain Deformation Near a Crack - Tip in a Power-Law Hardening Material. *J.Mech.Phys.Sol.*, 16, 1-12 (1968)
4. McClintock F.A., Plasticity Aspects of Fracture in "*Fracture*" (edited by H. Liebowitz), Vol.3, 47-225, Academic Press, New York (1971).

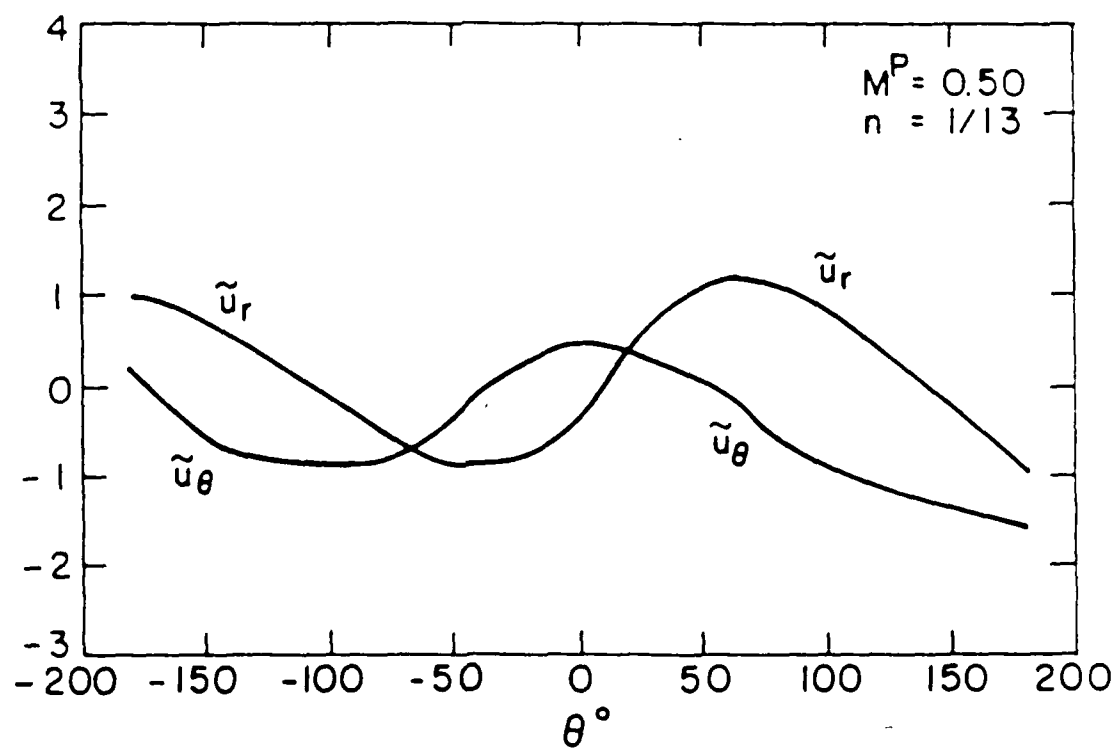
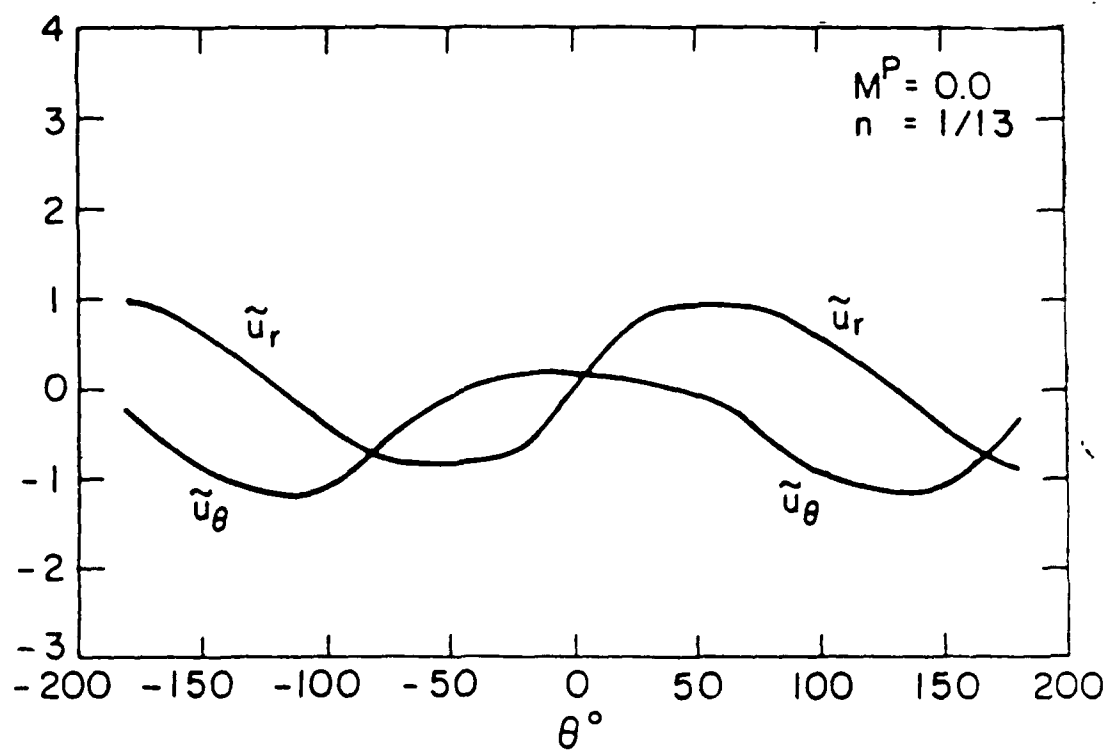


Figure 1 θ -variations for the displacement functions at the tip of a crack for plane strain, $n=1/13$, $M^P=0.0, 0.50$.

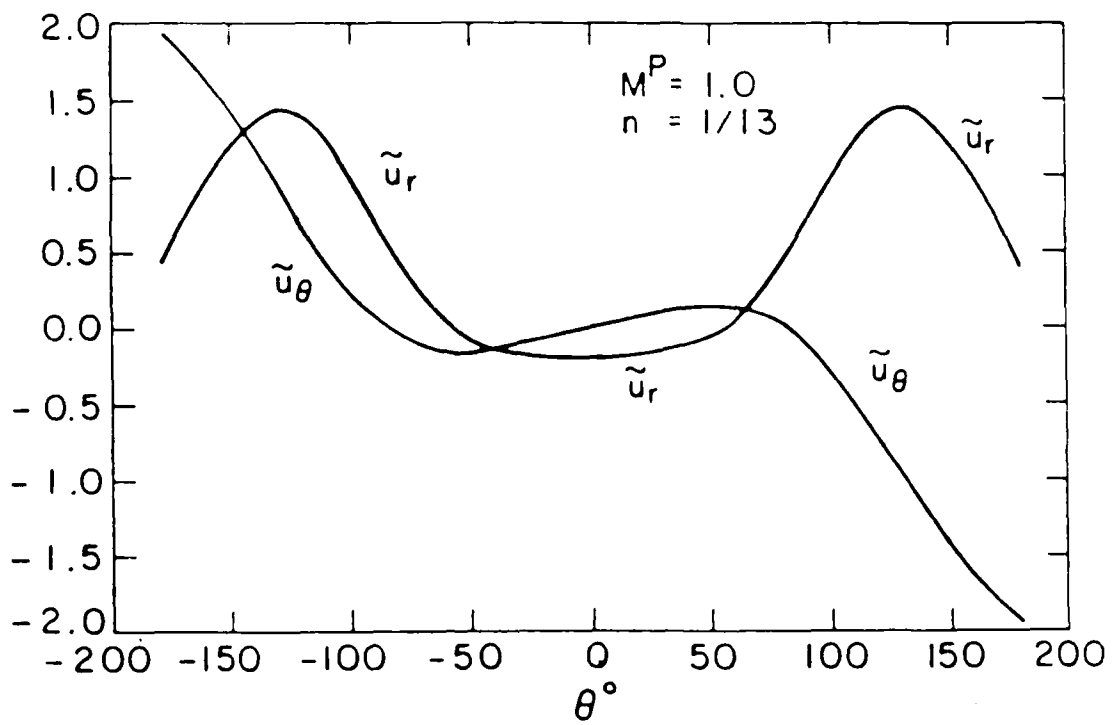
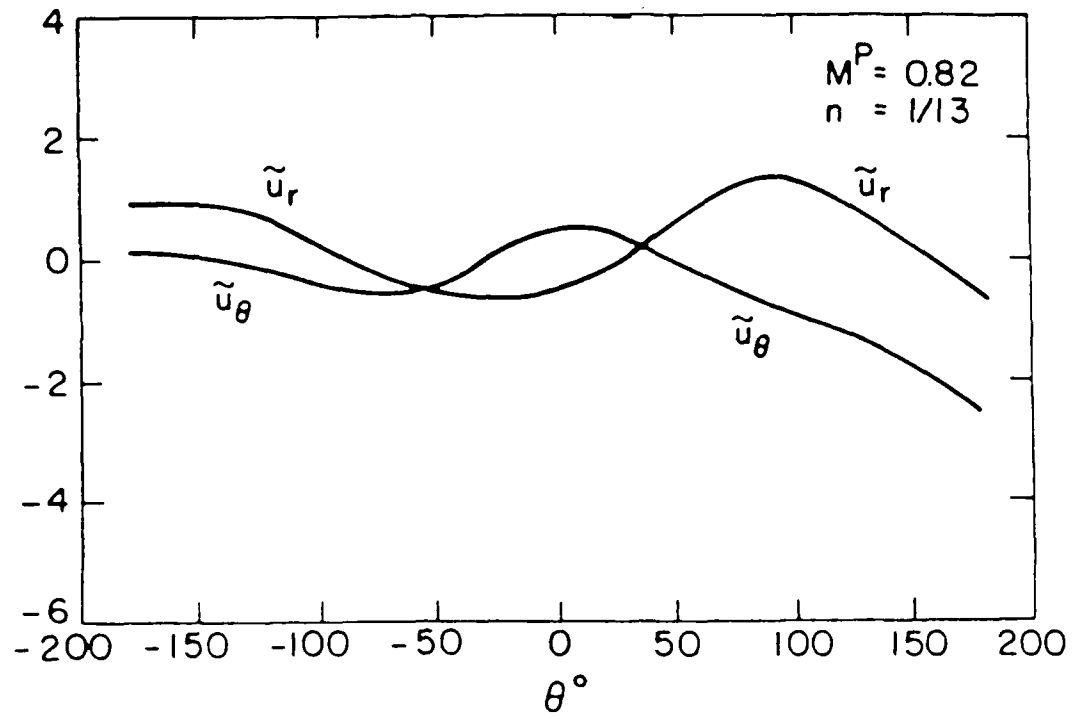


Figure 2 θ -variations for the displacement functions at the tip of a crack for plane strain, $n=1/13$, $M^P=0.82, 1.0$

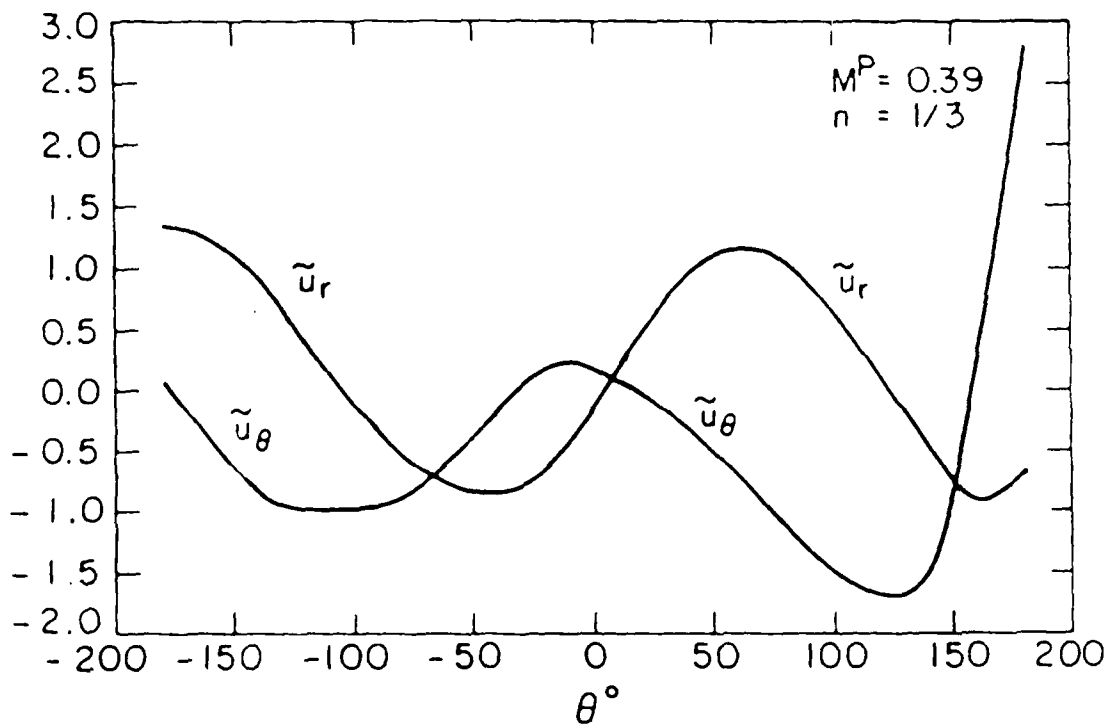
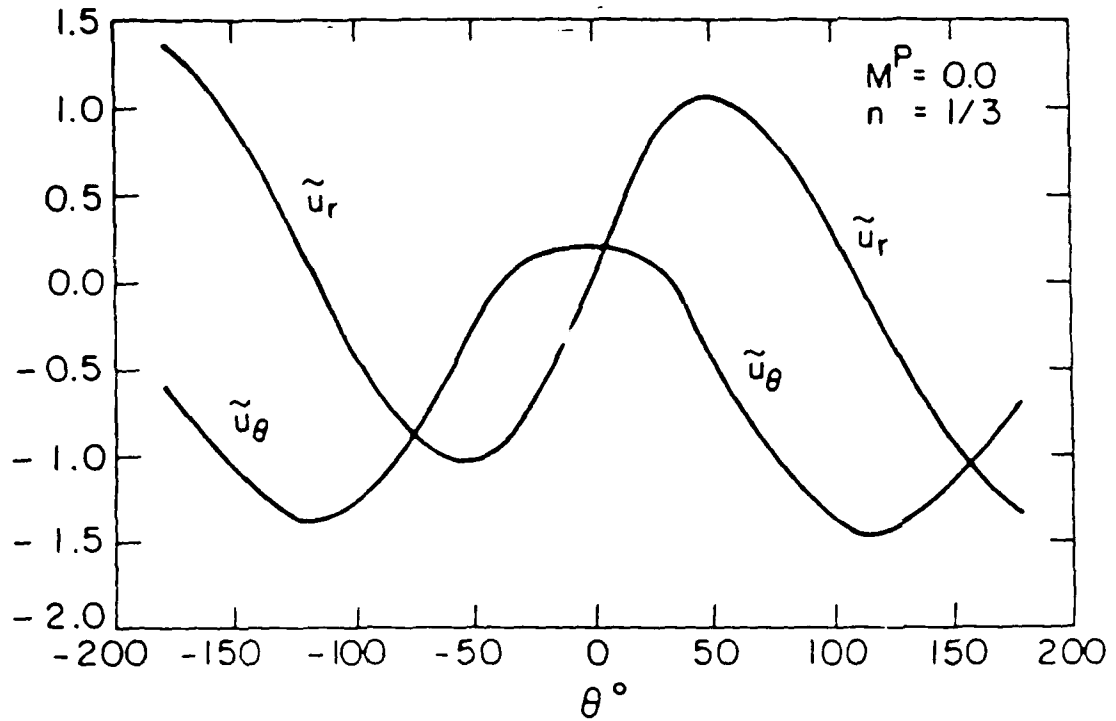


Figure 3 θ -variations for the displacement functions at the tip of a crack for plane strain, $n=1/3$, $M^P=0.0, 0.39$

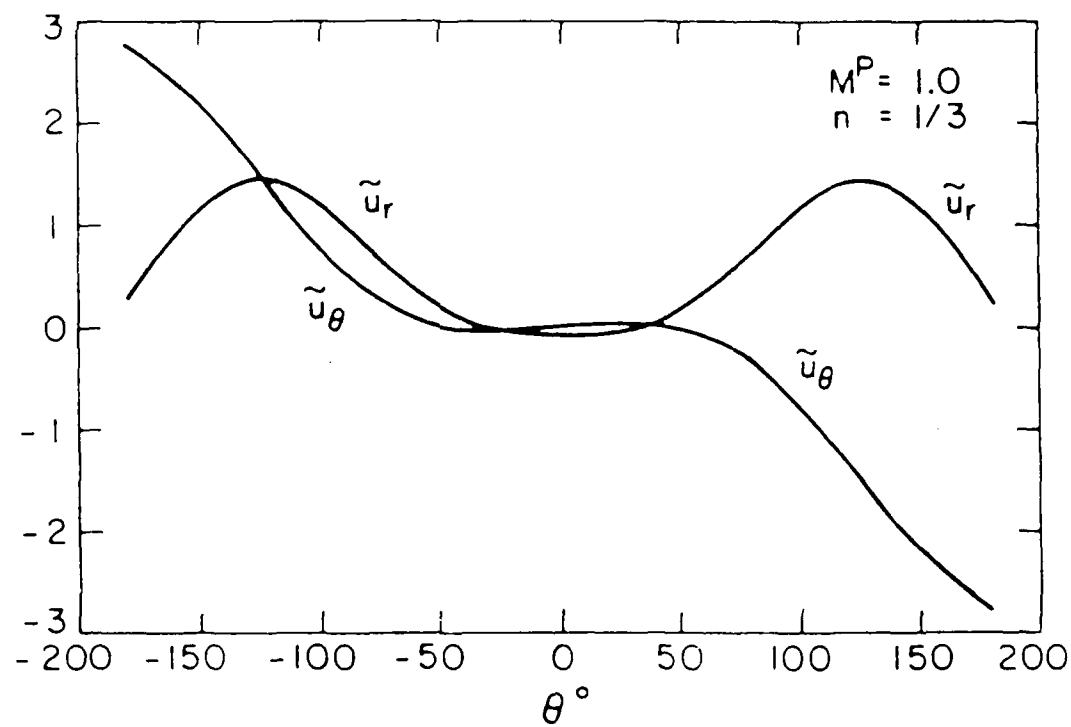
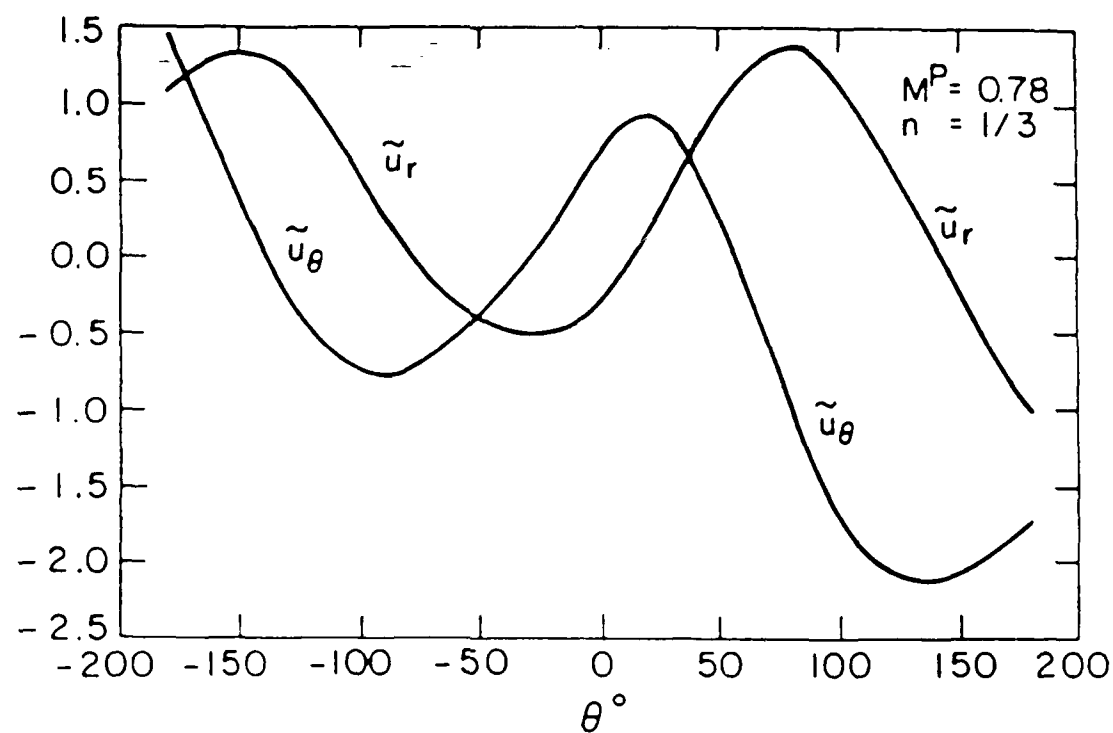


Figure 4 θ -variations for the displacement functions at the tip of a crack for plane strain, $n=1/3$, $M^P=0.78, 1.0$

END

DTIC

9-86