

AD-A174 226

FUSED SALT SYNTHESIS OF MATERIALS FOR IR (INFRARED)
WINDOWS(U) ROCKWELL INTERNATIONAL THOUSAND OAKS CA
SCIENCE CENTER P MORGAN ET AL OCT 86 SC5422 TR

1/1


UNCLASSIFIED

N00014-85-C-0140

F/G 11/2

NL



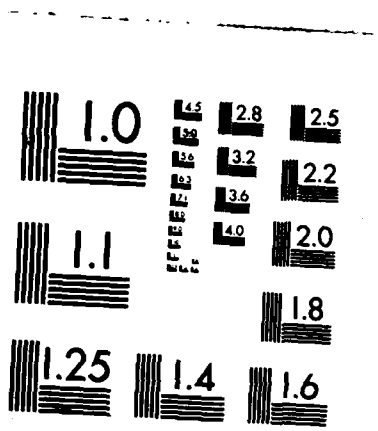

MICROCOPY RESOLUTION TEST CHART
 NATIONAL BUREAU OF STANDARDS-1963-A

12

SC5422.TR

SC5422.TR

Copy No. 72

AD-A174 226

FUSED SALT SYNTHESIS OF MATERIALS FOR IR WINDOWS

TECHNICAL REPORT NO. 1

CONTRACT NO. N00014-85-C-0140

Prepared for

Office of Naval Research
800 N. Quincy Street
Arlington, VA 22217-5000

P. Morgan
M.S. Koutsoutis

OCTOBER 1986

DTIC
ELECTE
NOV 21 1986
S B

Approved for public release; distribution unlimited



Rockwell International
Science Center

86 11 21 012

Science Center
Rockwell International Corporation
1049 Camino Dos Rios
P.O. Box 1085
Thousand Oaks, California 91360

(805) 373-4545



Rockwell
International

In reply refer to SC86-1281

November 18, 1986

Scientific Officer
Program Manager Non Metallic Materials
Engineering Sciences Program
Office of Naval Research
800 N. Quincy Street
Arlington, VA 22217-5000

Attn: Dr. Robert C. Pohanka

Subject: N00014-85-C-0140

The Technical Report No. 1 which was submitted to you on November 06, 1986, reflected incorrect information on the DD Form 1473. Enclosed you will find a "revised" copy of the Technical Report No. 1.

Please accept our apology for any inconvenience caused by this error. Should you have any questions, please contact the undersigned at area code (805) 373-4406.

Rockwell International Corporation

A handwritten signature in cursive script that reads "Susan L. McCarthy".

S.L. McCarthy
C & P Data Management

G.O. 5422

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS										
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION/AVAILABILITY OF REPORT Approved for public release; distribution unlimited.										
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE												
4. PERFORMING ORGANIZATION REPORT NUMBER(S) SC5422.TR		5. MONITORING ORGANIZATION REPORT NUMBER(S)										
6a. NAME OF PERFORMING ORGANIZATION Rockwell International Science Center	6b. OFFICE SYMBOL <i>(If applicable)</i>	7a. NAME OF MONITORING ORGANIZATION Naval Weapons Center										
6c. ADDRESS (City, State and ZIP Code) 1049 Camino Dos Rios Thousand Oaks, CA 91360		7b. ADDRESS (City, State and ZIP Code) Code 3854 China Lake, CA 93555-6001										
8a. NAME OF FUNDING/SPONSORING ORGANIZATION Office of Naval Research	8b. OFFICE SYMBOL <i>(If applicable)</i>	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER Contract No. N00014-85-C-0140										
8c. ADDRESS (City, State and ZIP Code) 800 N. Quincy Street Arlington, VA 22217-5000		10. SOURCE OF FUNDING NOS. <table border="1" style="width: 100%; border-collapse: collapse;"> <thead> <tr> <th style="width: 25%;">PROGRAM ELEMENT NO.</th> <th style="width: 25%;">PROJECT NO.</th> <th style="width: 25%;">TASK NO.</th> <th style="width: 25%;">WORK UNIT NO.</th> </tr> </thead> <tbody> <tr> <td> </td> <td> </td> <td> </td> <td> </td> </tr> </tbody> </table>		PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT NO.					
PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT NO.									
11. TITLE (Include Security Classification) FUSED SALT SYNTHESIS OF MATERIALS FOR IR WINDOWS												
12. PERSONAL AUTHOR(S) Morgan, P. and Koutsoutis, M.S.												
13a. TYPE OF REPORT Technical Report No. 1	13b. TIME COVERED FROM 1985 TO 1986	14. DATE OF REPORT (Yr., Mo., Day) OCTOBER 1986	15. PAGE COUNT 10									
16. SUPPLEMENTARY NOTATION To be submitted to Mat. Res. Bull.												
17. COSATI CODES <table border="1" style="width: 100%; border-collapse: collapse;"> <thead> <tr> <th style="width: 33%;">FIELD</th> <th style="width: 33%;">GROUP</th> <th style="width: 33%;">SUB. GR.</th> </tr> </thead> <tbody> <tr> <td> </td> <td> </td> <td> </td> </tr> <tr> <td> </td> <td> </td> <td> </td> </tr> </tbody> </table>		FIELD	GROUP	SUB. GR.							18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number) Chalcogenides, Fused Salt, Monosized Particle Infrared Windows.	
FIELD	GROUP	SUB. GR.										
19. ABSTRACT (Continue on reverse if necessary and identify by block number) This paper describes the production of narrow size distribution, NaLaS ₂ , for IR windows, using a fused salt technique.												
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS <input type="checkbox"/>		21. ABSTRACT SECURITY CLASSIFICATION Unclassified										
22a. NAME OF RESPONSIBLE INDIVIDUAL Dr. Robert C. Pohanka		22b. TELEPHONE NUMBER (Include Area Code) 202-696-4402	22c. OFFICE SYMBOL ONR									

copy to P.I.



INTRODUCTION

Fused salt synthesis of a chalcogenide powder for infrared (IR) window use in the 8-12 μm regime of the "atmospheric window" has been investigated. Materials for this application require erosion resistance, high hardness and strength with good thermal shock resistance. Oxides, with the required mechanical properties, because of their strong M-O bonds, especially when M is a light element, however, absorb in this region and a more massive anion is required.

As narrow bandgap materials will not fill the bill, especially at higher temperatures, one is left apparently with only the more ionic chalcogenides or pnictides. One considers, therefore, bonds such as Zn-Se, Ca-S, La-S, Zn-P, and a few others. The choices are few, as chalcogenide or pnictide bonds are less strong, leading to weaker and softer structures with higher thermal expansivity. Thermal expansivity in an approximately close-packed structure is proportional to individual bond valence.¹ Total strength can be related to total bond valence sum at the "cations and anions". The bonding requirements are therefore in conflict; strong bonds between light atoms are needed for mechanical properties, and weak bonds between heavier elements for IR transmittance. Compromise is the only solution.

Attempts at compromise have included $\text{Zn}^{\text{IV}}\text{S}^{\text{IV}}\text{P}_2^{\text{IV}}$ (Wurtzite type)² (Roman numerals denote atom coordination). The idea here is to use low coordination with stronger bonds (to keep thermal expansion down). Unfortunately, the absorption edge is too low.³ An alternative is to attempt to use many weaker bonds as in $\text{Ca}^{\text{VIII}}\text{La}_2^{\text{VIII}}\text{S}_4^{\text{VI}}$ (Th_3P_4 structure type),^{4,5} however, the thermal expansivity is high as each bond valence is low.

One possible compromise, as discussed here, may be to use a six coordinated solid such as $\text{Na}^{\text{VI}}\text{La}^{\text{VI}}\text{S}_2^{\text{VI}}$

For the 3-5 μm "atmospheric window", various oxides and nitrides, Y_2O_3 , MgAl_2O_4 , AlN and AlON , have been tried and sophisticated processing techniques⁶ have been designed to fabricate them. This will be true for the 8-12 μm candidates.



A-1





SC5422.TR

It has become recognized that one efficient way of producing high-density, fine-grain oxide ceramics is to start with uniformly highly compacted monosize particles.⁷ The aim is to achieve large numbers of particle-particle contacts, with uniform densification during sintering, so as to avoid the formation of large voids due to discontinuous effects,⁸ this danger has been recognized for many years, but only recently studied in detail. Voids, especially larger ones, are sources of fracture initiation and light scattering. In the case of an IR window, if unavoidable pores can be kept below the size corresponding to the wavelength of interest, then transparency will be little affected. This should be easy for the 8-12 μm regime of interest.

Less work has been done to produce chalcogenides of uniform particle size than for the case of oxides;⁹ for complex mixed chalcogenides, new challenges are expected. A further advantage of carefully controlled growth of uniform particles should be improvements in purity of the product. This is especially important with respect to oxygen, ubiquitously property degrading, but unfortunately almost ever-present. It is anticipated that uniform particles of complex chalcogenides or other appropriate IR transparent materials should be readily fabricable into IR windows.


Many chalcogenides, due to their more covalent nature, and therefore lower bulk and grain boundary diffusion values relative to coarsening mechanisms such as evaporation-condensation, do not readily sinter¹⁰ (if at all) and must be hot-pressed or HIPed (hot iso-pressed). It is extremely desirable to keep temperatures of fabrication low to avoid simultaneous grain coarsening, and hence mechanical weakening, and thus minimize evaporation-condensation and stoichiometry variation.

For this work, we have chosen the fused salt synthesis technique¹¹⁻¹⁴ for producing chalcogenides or pnictides with the aim of attaining controlled monosized particles in the 0.1-1 μm size range. The fused salt technique promises to be a better method of attaining good stoichiometry with high impurity and low oxygen content, which has been a persistent problem.¹⁵ This follows because the impurities and oxygen will tend to accumulate in the fused melt, while the particles are purified by solution-reprecipitation (Oswald ripening). The particles do not need to be milled (normally necessary to break up aggregates), thus eliminating a contaminating step. Initially, to establish the principles of the method, we attempted to use CaLa_2S_4 as a prototype candidate. A surprise result led us instead to study NaLaS_2 .



EXPERIMENTAL AND RESULTS


We wish to concentrate on cheap starting materials, potentially to be scaled up for later commercial use. We want the least number of steps to minimize labor, handling and contamination. Irreducibly simple, then, seemed to be the reaction in quartz inside a controlled atmosphere tube furnace:

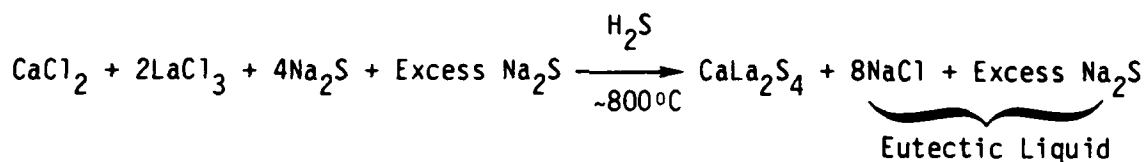

With many tries, varying the ratios of the ingredients, surprisingly, no CaLa_2S_4 was seen. Instead, recently discovered¹⁶ rock salt structure NaLaS_2 and CaS were the predominant products. Even more surprising to us was that when the by-product $\text{NaCl} + \text{Na}_2\text{S}$ was extracted by solution in cold water, the NaLaS_2 was not noticeably attacked. Contaminant $\text{La}_2\text{O}_2\text{S}$, present in the preparation and not produced by reaction with the water, was seen, suggesting a method of further lowering the oxygen potential, beyond that achievable by H_2S , was needed. It was further observed that, indeed, the $\text{NaCl}-\text{Na}_2\text{S}$ eutectic was in the region of 800°C (the $\text{NaCl}-\text{Na}_2\text{S}$ phase diagram has not been done!).

NaLaS_2 has the rock salt structure, i.e., $\overset{\text{VI}}{\text{Na}} \overset{\text{VI}}{\text{La}} \overset{\text{VI}}{\text{S}_2}$; thus, its six-fold coordinated structure may give usably low thermal expansivity while still having weak enough bonds for the absorption edge to be at a sufficiently long wavelength. In any event, it represented a new candidate for further study of the method.

The incredibly simple reaction:

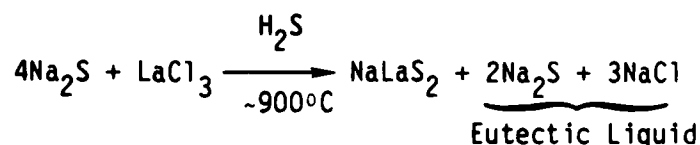



SC5422.TR

was used with the slightly higher temperature. Again, $\text{La}_2\text{O}_2\text{S}$ appeared as a low-level impurity and varying ratios of ingredients did not remove it.

To reduce oxygen further, the test was redone in carbon disulfide vapor by bubbling argon gas through CS_2 liquid. It was considered that this might produce some carbon deposits (it didn't), but even should they form with this method, the carbon would form floating on the fused salt, and thus be easily removed. It was found that by using a ratio of 2:1 $\text{Na}_2\text{S}:\text{LaCl}_3$, almost pure NaLaS_2 was achieved (< 5% of $\text{La}_2\text{O}_2\text{S}$ remained). At this point, alternative extraction studies were commenced. It was found that ethanol effectively removed NaCl and Na_2S in a Soxhlet extraction under argon, but that the method was extremely slow with > 10 g amounts. If water was used for at least one day in a Soxhlet, NaLaS_2 was decomposed (the water was ~ 60°C in this case).

Using a ratio of 2:1, Na_2S to LaCl_3 , produced purer NaLaS_2 with only a trace of $\text{La}_2\text{O}_2\text{S}$ after 7 h under CS_2 . If the mix was held for one day at 900°C in CS_2 , then La_2S_3 was a minor impurity.

At this point, another minor impurity was encountered whose presence increased with more excess Na_2S (desirable to produce a lower melting flux - easier to dissolve in organic solvents). It was found that the impurity could be isolated from the mixed NaLaS_2 /impurity product by treating with cold acetic acid which dissolves NaLaS_2 . The impurity was examined by energy dispersive x-ray fluorescence (EDS) which indicated La, Na (trace), Si and S. Material purified in this way was x-rayed; the diffraction pattern was analyzed by computer unit cell finders and turned out to be a (new) apatite structure, $\approx\text{Na}_{0.5}\text{La}_{4.5}(\text{SiO}_4)_3\text{S}$, hexagonal $\text{P6}_3/\text{m}$, $a = 9.911\text{\AA}$, $c = 7.025\text{\AA}$, $c/a = 0.709$.

After heating in air to 1000°C, the apatite became more poorly crystalline with cell parameters: $a = 9.874\text{\AA}$, $c = 7.016\text{\AA}$ and $c/a = 0.711$. For the known $\text{NaLa}_4(\text{SiO}_4)_3\text{F}$:¹⁷ $a = 9.689\text{\AA}$, $c = 7.1805\text{\AA}$ and $c/a = 0.741$. For a group of apatites,¹⁸ it is known that the c/a ratio falls when the trigonal site in apatite, i.e., the F site in $\text{NaLa}_4(\text{SiO}_4)_3\text{F}$, is occupied by a larger anion such as Cl. In our case, the c/a ratio indicates that the detected sulfur is probably in this site, as suggested above. We believe this is the first known apatite of this type. Naturally, the finding of Si in the impurity suggested that Na_2S , especially in excess, was attacking the quartz containers used to



SC5422.TR

contain the flux melt. We therefore switched to using carbon crucibles. At this point, no further impurity was seen, and the Na_2S content was conveniently increased to about 2:1 $\text{Na}_2\text{S}:\text{NaCl}$ in the flux.

Samples of NaLaS_2 , which have been standing in ambient air for 14 months, still give XRD patterns that appear to be unchanged from the originals. However, NaLaS_2 is attacked by hot water, so continuing studies have been carried out to remove the growth flux with organic solvents. We have found $\text{C}_2\text{H}_5\text{OH}$ to be effective, but slow in a Soxhlet extraction. We now favor dimethyl formamide, DMF, $\text{HCON}(\text{CH}_3)_2$ in a well thermally insulated system where the Soxhlet thimble is at about 140°C . A resulting preparation of x-ray pure NaLaS_2 is shown in the accompanying photograph, where well-rounded $10\ \mu\text{m}$ "apples" of NaLaS_2 are shown (the reason for the curious shape is unknown). To obtain the desired $\approx 1\ \mu\text{m}$ size spheres, we will have to go to much shorter times of Oswald ripening. This is an immediate future task.

As an example of the relative uniformity in NaLaS_2 product, Figure 1 shows SEM pictures of the product at indicated magnifications after extraction of the eutectic melt with cold water. The slight surface "contaminant" may be due to reaction with the water.

CONCLUSION

→ This type of very simple fused salt chemistry appears to be a viable approach to modern ceramic synthesis of monosize particles of complex sulfides or other chalcogenides. ↙

ACKNOWLEDGEMENT

This research was supported by the Office of Naval Research and by the Rockwell International Science Center Youth Motivation Program.



SC37781



Figure 1 SEM of particles of NaLaS_2 .



REFERENCES

1. R.M. Hazen and L.W. Finger, Comparative Crystal Chemistry, Wiley-Interscience (1982).
2. J. Covino, "Synthesis and Characterizations of Phosphides as Potential IR Transmitting Ceramics," Proc. Int. Soc. for Opt. Eng. 505, Emerging Optical Materials, Aug. 21-24, 1984.
3. G.Q. Yao, H.S. Shen, R. Kershaw, K. Dwight and A. Wold, "Preparation and Characterization of $ZnSiP_2$ and $ZnGeP_2$ Single Crystals," Technical Report No. 1, Office of Naval Research, Contract No. N00014-85-K-0177 (1986).
4. W.B. White, D. Chess, C.A. Chess and J.V. Biggers, " $CaLa_2S_4$: Ceramic Window Material for the 8 to 14 μm Region," SPIE 297, 38-43 (1981).
5. K.J. Saunders and R.L. Gentilman, "Fabrication Studies of Ternary Rare-Earth Sulfides for Infrared Applications," Final Technical Report, Office of Naval Research, Contract No. N00014-82-C-0413 (1984).
6. W.H. Rhodes, "Controlled Transient Solid Second-Phase Sintering of Yttria," J. Am. Ceram. Soc. 64, 13-19 (1981).
7. E.A. Barringer and H.K. Bowen, "Formation, Packing and Sintering of Monodisperse TiO_2 Powders," J. Am. Ceram. Soc. 65 (12), C199-C201 (1982).
8. K.D. Reeve, "Nonuniform Shrinkage in Sintering," Am. Ceram. Soc. Bull. 42 (8), 452 (1963).
9. E. Matijevitch, "Monodispersed Colloidal Metal Oxides, Sulfides and Phosphates, 334-52, Ultrastructure Processing of Ceramics, Glasses and Composites, eds., L.L. Hench and D.R. Ulrich, Wiley (1984).
10. P.E.D. Morgan, "The Sintering of Zinc and Cadmium Sulfides," Sintering and Related Phenomena, Proc. Int. Conf., Notre Dame, IN (1965); 861-94, ed., G.C. Kruzynski, Gordon and Breach (1967).
11. D.G. Wickham, "The Preparation of Ferrites with the Aid of Fused Salts," Ferrites, 105-7, Proc. Int. Conf., Kyoto, Japan (1970).
12. P.J. Walker and R.C.C. Ward, "The Preparation of Some Ternary Sulfides MR_2S_4 ($M = Ca, Cd$; $R = La, Sm, Er$) and the Melt Growth of $CaLa_2S_4$," Mat. Res. Bull. 19, 717-725 (1984).



SC5422.TR

13. V.V. Leonov, "Crystallization of Cadmium Sulfide from a Cadmium Chloride Melt," *Inorganic Materials* 19, 1238-9 (1983).
14. H.J. Scheel, "Crystallization of Sulfides from Alkali Polysulfide Fluxes," *J. Crystal Growth* 24/25, 669-73 (1974).
15. K.L. Lewis, J.A. Savage, K.J. Marsh and A.P.C. Jones, "Recent Developments in the Fabrication of Rare-Earth Chalcogenide Materials for InfraRed Optical Applications," *Proc. SPIE* 400, 21-28 (1983).
16. M. Sato, G. Adachi and J. Shiokawa, "Preparation of Sodium Rare-Earth Sulfides, NaLnS_2 (Ln; Rare-Earth Elements)," *Mat. Res. Bull.* 19, 1215-1220 (1984).
17. PDF No. 21-1364, Center for Powder Diffraction Standards, Swarthmore, PA.
18. O.S. Bondareva and Yu. A. Malinovskii, "Crystal Structure of Synthetic Ba Hydroxy Apatite," *Sov. Phys. Cryst.* 31 (2), 136-138 (1986).

END

1-87

DTIC