


AD-A174 685



US ARMY
MATERIEL
COMMAND

AD

12

MEMORANDUM REPORT BRL-MR-3521

**QUASI-STATIC COMPRESSION AND TENSILE
STRESS-STRAIN CURVES, TANTALUM - 10%
TUNGSTEN AND 300 GRADE MARAGING STEEL**

**Ralph F. Benck
Graham F. Silsby**

May 1986

**DTIC
ELECTE
DEC 03 1986**
S D

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED.

**US ARMY BALLISTIC RESEARCH LABORATORY
ABERDEEN PROVING GROUND, MARYLAND**

DTIC FILE COPY

86 12 03 001

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM												
1. REPORT NUMBER Memorandum Report 3521	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER												
4. TITLE (and Subtitle) Quasi-static Compression and Tensile Stress-strain Curves, Tantalum - 10% Tungsten and 300 Grade Maraging Steel		5. TYPE OF REPORT & PERIOD COVERED FINAL												
		6. PERFORMING ORG. REPORT NUMBER												
7. AUTHOR(s) Ralph F. Benck Graham F. Silsby		8. CONTRACT OR GRANT NUMBER(s)												
9. PERFORMING ORGANIZATION NAME AND ADDRESS US Army Ballistic Research Laboratory ATTN: SLCBR-TB Aberdeen Proving Ground, MD 21005-5066		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS RDT&E 1L162618AH80												
11. CONTROLLING OFFICE NAME AND ADDRESS US Army Ballistic Research Laboratory ATTN: SLCBR-DD-T Aberdeen Proving Ground, MD 21005-5066		12. REPORT DATE May 1986												
		13. NUMBER OF PAGES												
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) UNCLASSIFIED												
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE												
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.														
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)														
18. SUPPLEMENTARY NOTES														
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) <table border="0"> <tr> <td>Materials Properties</td> <td>Penetrators</td> <td>Yield Strength</td> </tr> <tr> <td>Maraging Steel</td> <td>Projectiles</td> <td>Poisson's Ratio</td> </tr> <tr> <td>Tantalum Alloy</td> <td>Terminal Ballistics</td> <td>Elastic Modulus</td> </tr> <tr> <td>Stress-strain curves</td> <td>Young's Modulus</td> <td></td> </tr> </table>			Materials Properties	Penetrators	Yield Strength	Maraging Steel	Projectiles	Poisson's Ratio	Tantalum Alloy	Terminal Ballistics	Elastic Modulus	Stress-strain curves	Young's Modulus	
Materials Properties	Penetrators	Yield Strength												
Maraging Steel	Projectiles	Poisson's Ratio												
Tantalum Alloy	Terminal Ballistics	Elastic Modulus												
Stress-strain curves	Young's Modulus													
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) This report presents the results of quasi-static compression and tension tests of tantalum -10% tungsten alloy and Vascomax 300 CVM 300 grade maraging steel. Young's modulus, Poisson's ratio, and yield strength and ultimate strength were determined at test temperatures of 23.9°C. Results provide engineering properties documentation for materials used in several terminal ballistic tests.														

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

TABLE OF CONTENTS

	Page
LIST OF ILLUSTRATIONS	5
LIST OF TABLES	7
I. INTRODUCTION	9
II. MATERIALS	9
III. TEST PROCEDURES	14
IV. GRIP TESTS	16
V. DATA REDUCTION PROCEDURES	17
VI. RESULTS	22
VII. ACKNOWLEDGEMENTS	28
REFERENCES	31
APPENDIX	33
DISTRIBUTION LIST	37



Accession For	
NTIS CRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

LIST OF ILLUSTRATIONS

Figure		Page
1	Longitudinal Sections of Annealed Ta-10W Bar	11
2	Transverse Sections of Annealed Ta-10W Bar	12
3	Embossing of 1/4 Inch Diameter Work-hardened Ta-10W Bar Specimen by Serrated Grips (Test T200)	18
4	Fractured Fully Work-hardened Ta-10W Grip Test Specimen (Test T200)	19
5	Data Plots from Grip Test of Fully Work-hardened Ta-10W Specimen (Test T200)	20
6	Individual Measured and Corrected Engineering Stress versus Engineering Strain Curves, to Rupture, for Annealed Ta-10W in Tension, from Tests T108 and T109	25
7	Average Engineering Stress versus Engineering Strain, to 7% Strain, for Annealed Ta-10W in Tension, from Tests T107 thru T109	25
8	Engineering Stress versus Engineering Strain for Annealed Ta-10W in Compression from Test C105	26
9	Engineering Stress versus Engineering Strain, to Rupture, for Fully Work-hardened Ta-10W in Tension, from Test T110	26
10	Measured and Corrected Engineering Stress versus Engineering Strain, to Rupture, for Precipitation Hardened 300 Maraging Steel in Tension, from Test T115	27
11	True Stress versus True Strain, to Rupture, for Precipitation Hardened 300 Maraging Steel in Tension, from Test T115	27
12	Average Engineering Stress versus Engineering Strain for Precipitation Hardened 300 Maraging Steel in Compression from Tests C111 thru C113	28
13	Post-test Ta-10W Tensile Specimens	29
14	Post-Test Ta-10W and 300 Maraging Steel Tensile Specimens	30

LIST OF TABLES

Table		Page
1	Reported Ingot Analyses for Three Ta-10W Samples	10
2	Hardness Conversions for Nickel Alloys	13
3	Experimental Parameters	15
4	Measured Material Properties	23
5	Measured (Photographic) and Corrected Engineering Strain at Rupture	24
A1	Engineering Strain and Engineering Stress for Ta-10W Specimens, Measured on Tensile Tests T108 thru T110	35
A2	Engineering Strain and Engineering Stress for 300 Maraging Steel Specimens, Measured Photographically on Tensile Tests T114 and T115	36

I. INTRODUCTION

This report documents the results of quasi-static tensile and compression tests of a commercially available tantalum-10 percent tungsten alloy (Ta-10W) and a commercially available maraging steel. These two alloys were used in projectiles of a number of designs for laboratory ballistic tests. Experimentally determined Young's modulus, Poisson's ratio, yield and ultimate strengths, and engineering and true stress-true strain curves are presented. The tests were conducted for the Penetration Mechanics Branch (PMB), Terminal Ballistics Division (TBD), Ballistic Research Laboratory (BRL), by the Solid Mechanics Branch (SMB), TBD. This effort is part of SMB's Core Materials Program, and this report is one in a series of reports [references 1-8] characterizing the material properties of armor and penetrator materials. The data are useful for the design of projectiles, and the idealized stress-strain curves are used to improve the materials' characterization in existing and future finite element computer codes modeling the penetration process.

II. MATERIALS

The tantalum alloy was used alone in long rod penetrators for ordnance velocity phenomenology firings as a generic commercially available high density metal. It was investigated as a practical substitute for ballistic tungsten or uranium alloys. It was also used as a core material in two conceptual increased velocity projectiles designed to be launched from a weaponized light gas gun. The increased velocity projectiles had conical flight bodies. A thin skirt of 300 grade maraging steel with a central hub or sheath carried a tantalum alloy core. On the air defense version, firings were primarily conducted to determine values for aeroballistic coefficients, with proof-of-concept targets for terminal effects mounted at the end of the flight tunnel. The tantalum alloy was in the form of ballast slugs. On the anti-armor version, a tantalum-alloy rod formed a full-length penetrator along the central axis of the round.

Test specimens were machined from five tantalum bars. Material certifications were available for those from two lots, and are reported in Table 1. Work hardening is the only practical hardening mechanism for this alloy. The bar properties result from the amount of cold working following the last process anneal: the more reduction in area, the higher the yield strength and the lower the elongation to rupture [9]. Subsequent stress relief, recrystallization, or annealing causes reduction in yield and increase in elongation to rupture. Commercial practice is to supply Ta-10W bar either in the as-rolled (fully work hardened) or in the fully annealed condition, unless the purchaser makes special arrangements with the supplier. Therefore, the assumption is made that the uncertified bars are in one of these two conditions.

To check the microscopic structure of the material, longitudinal and transverse specimens of the annealed 3/8 inch (9.52 mm) diameter Teledyne Wah Chang bar used in test T152 were sectioned, polished, and etched five minutes in a solution made by mixing 30 millilitres each of concentrated hydrofluoric acid, concentrated sulfuric acid, and water, to which five drops of an aqueous solution of 30 percent hydrogen peroxide was added. Representative micrographs are presented in Figures 1 and 2. In addition, 1000 gram Tukon micro-hardness measurements were made on the transverse section, yielding Knoop hardness

Table 1. Reported Ingot Analyses for Three Ta-10W Samples

Producer	Fansteel	Teledyne/Wah Chang Albany
Bar Diameter	1/2 Inch	3/8-Inch
Production Order No.	644-W31619-0	6827
Heat/Lot No.	60B-3S32	620297 Ta-10W
Certificate Date	10 Dec 75	5 May 76
Ingot Brinell		High 197
Hardness Number		Average 194
3Kg Load		Low 189
Sample Location	Unspecified	Top Bottom

Alloying Elements	Composition		
	Balance	Balance	Balance
Ta			
W	9.48%	10.1%	10.3%
Impurities (PPM)			
H	<5	<5	<5
C	<10	<30	<30
N	12	<5	7
O	41	<50	60
Si		<40	<40
Ti	<20		
V	<20	<20	<20
Cr	<10	<20	<20
Fe	<20	<40	<40
Co	<20	<10	<10
Ni	<20	<20	<20
Cu		<40	<40
Zr	<20		
Cb(Nb)	650	<20	<20
Mo	<20	<20	<20

Notes:

1. The bar chemistry can be expected to be higher in hydrogen, nitrogen, oxygen, and possibly carbon by virtue of the metal's affinity for, and its exposure to, these elements during processing from the ingot into the bar product.
2. Data are from certificates accompanying the material.

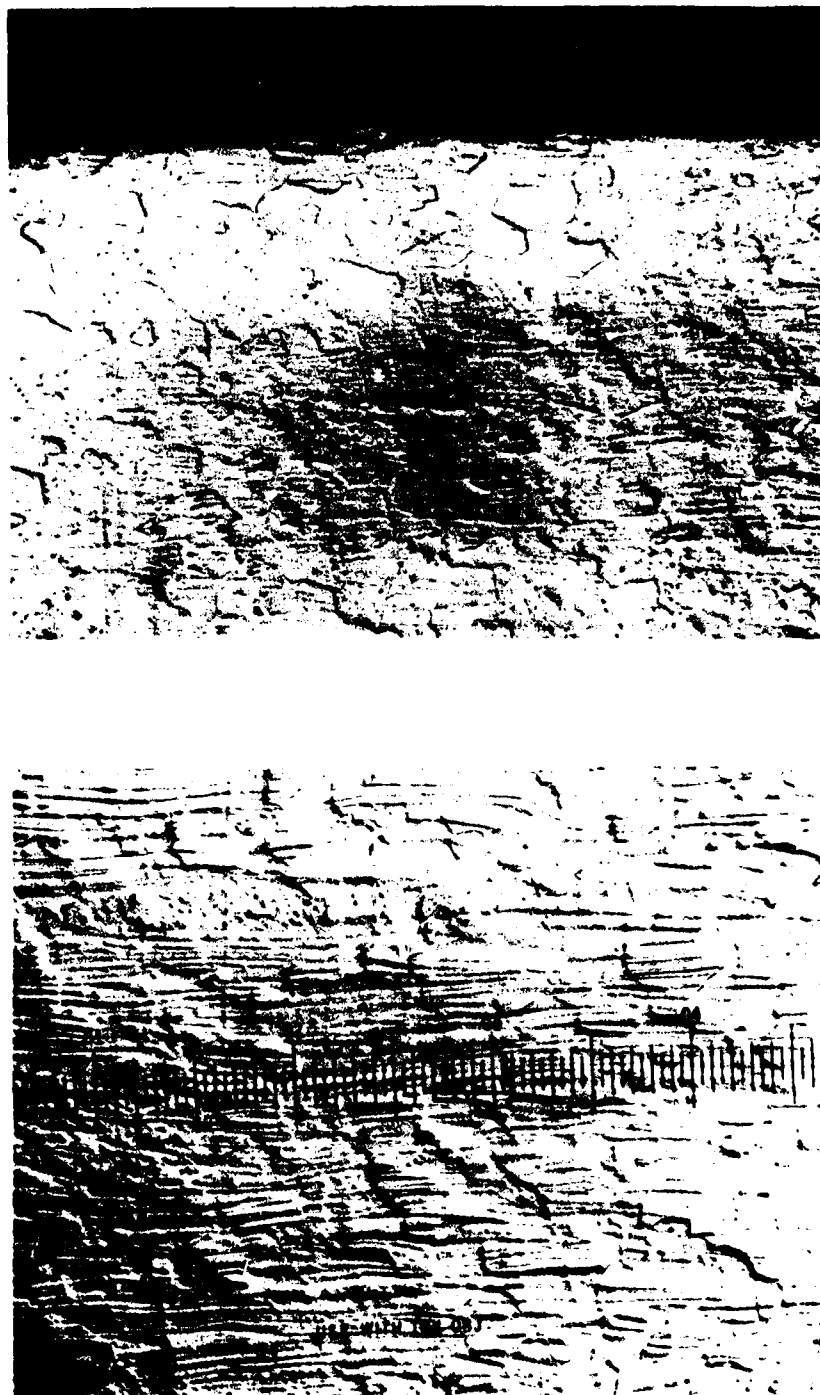


Figure 1. Longitudinal Sections of Annealed Ta-10W Bar. Bar was used on tensile test T152. Top photo is from edge and bottom photo is from middle of bar. Reticle is graduated in inches.

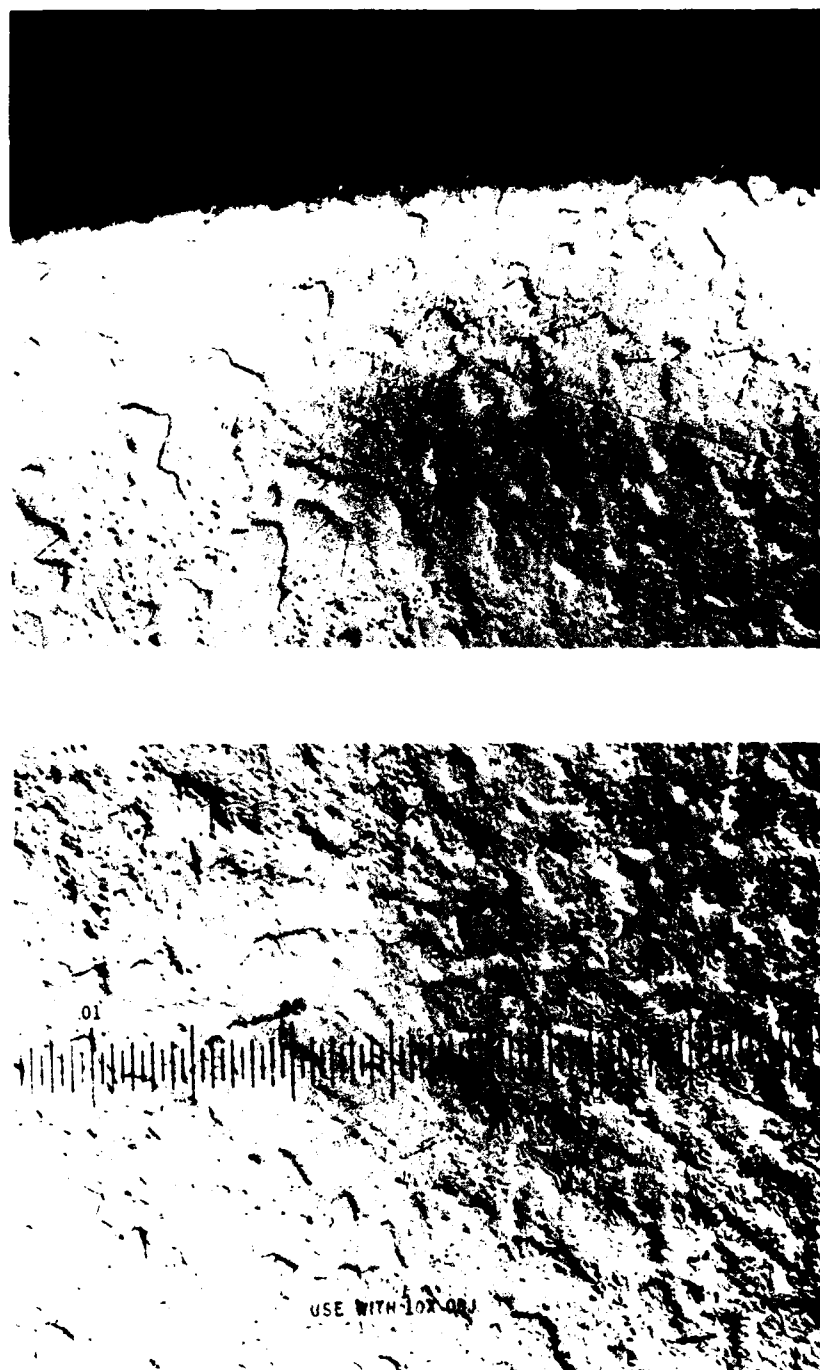


Figure 2. Transverse Sections of Annealed Ta-10W Bar. Bar was used on tensile test T152. Top photo is at the edge of the bar and bottom photo is from the middle of the bar. Specimen is overetched. Reticle is graduated in inches.

numbers. There was no significant difference in hardness with position in the section. The average hardness (total of 20 impressions) was 227.7 Knoop. It seems as if every hardness measurement reported in the literature is based on a different scale. To provide some feeling for the relationship between hardnesses on several commonly used scales, Table 2 is presented. It was prepared from relevant portions of two tables in reference 10 for nickel alloys. We believe these to be the best figures readily available with which to compare the hardnesses of tantalum alloys. It should be remembered that the hardness measured is a function of the indenter and sample geometry, the applied load, and the material indented, so values will be approximate.

Table 2. Hardness Conversions for Nickel Alloys
(From Reference 10)

Knoop 1000 g Knoop Indenter	Vickers 10 kg Vickers Indenter	Rockwell B 100 kg 1.588 mm Ball	Rockwell C 150 kg Diamond Indenter	Brinell 3000 kg 10 mm Standard Ball
204	179	88	<6.5>	176
215	188	90	<9.0>	184
226	198	92	<12.0>	194
239	209	94	<14.5>	204
251	220	96	<17.0>	215
267	234	98	20.0	228
283	248	100	22.5	241
304	266	<102>	25.5	258

Note: Values in brackets fall outside recommended ranges of applicability.

The 300 maraging steel tested is without certification. The specimens are from the same bar from which the projectiles were fabricated. The test results support a conclusion that the material is indeed a 300 maraging steel. The hardening process in maraging steels is to solution anneal the material by heating to 820 °C to convert the structure to austenite and then to air cool thru an M_f of 1000 °C, at which essentially all of the structure has finished its transformation back to martensite. Reheating to 480 °C and holding for six hours strengthens the material by precipitation and an order-disorder reaction. Considerable variation in temperature and time at temperature will not seriously affect the material properties. Although there is some variation in properties with rolling direction, the only practical way to significantly change the yield strength is to change the composition. Hence, the yield strength when hard indicates which grade of maraging steel is being used. In this case, the average yield strength of 2079 plus or minus 76 MPa is essentially indistinguishable from the typical value of 1996 MPa for a 300 maraging steel given in reference 11, versus the typical value of 1750 MPa cited for 250 maraging steel, the next closest grade.

III. TEST PROCEDURES

The testing apparatus, procedures, and data reduction regimen have been reported previously in references 1, 2, 6, and 7, and are in general accord with the ANS standards [13, 14]. The test specimen geometries, however, are quite variable. The specimens in general must be prepared from available material, which is frequently too short and too small in diameter to prepare standard specimens. The limited number of grips which we have for our testing machine likewise constrains overall specimen geometry. Because the elongation to rupture is sensitive both to the processing history of the bar from which the sample is taken, and to the specimen size, it is desirable to select a single standard specimen diameter so as to measure the former value without the influence of variations in the latter. With the exception of two tensile specimens (T152 and T153) for which the nominal reduced section diameter was 5.05 mm, this was accomplished using a 1/4 inch (6.35 mm) nominal reduced section diameter. The compression specimens were likewise nominally 1/4 inch diameter and 3/4 inch long (19.05 mm). All of the specimens were machined with the final cut being no deeper than 0.13 mm and the circumferential tool marks were removed by polishing with emery paper followed by crocus cloth. The surface finish was 0.8 micrometre RMS or less, with the lay about 45 degrees in both directions to the specimen axes.

The stress for each specimen was measured by recording the output of a load cell. All the specimens except the one used for the grip test (discussed later) were instrumented with adhesive bonded (M-Bond 200) foil resistance strain gages (BLH type FAET 06D-12 PEL). The strain was not expected to exceed 10 percent, so that no other strain measuring technique was used on the initial Ta-10W tensile test, T107. The tantalum alloy proved to be considerably more ductile than that, so that the strain record is incomplete on this specimen. Following that, an assortment of strain measuring techniques was used. Because the size of the material available for testing was frequently minimal, the specimens were frequently shorter than desirable. Where the reduced section length and end geometry permitted, a one inch extensometer was the preferred strain measuring means. Otherwise, the gage marks were scribed on the tensile specimens and were periodically photographed during the progress of the test. On the 5.05 mm diameter reduced section specimens, a one-half inch extensometer was used in addition to photographing scribed gage marks. The gage marks were frequently spaced less than four specimen diameters apart, so that the tensile strain data had to be corrected to a standard gage spacing before being further reduced. Tensile tests were continued to specimen fracture, while compression tests were terminated at gage failure or extensive specimen bending. The hardness of most of the specimens was measured. Where the impression was made on a cylindrical surface, the hardness was corrected to that which would have been measured on a flat surface, in accordance with USA Standard Z115.6-1967 [15]. All of the tests were performed at a constant 23.9 degrees Celsius, while the relative humidity varied from 33 to 49 percent. A summary of the pertinent experimental parameters is presented in Table 3.

Table 3. Experimental Parameters

Material	Bar Dia. (inch)	Source ^a	Test ^b Type & No.	Additional ^c Instru- mentation	Hard- ^d ness (HRC)	Sample or Gage Length (mm)	Sample or Reduced Diameter (mm)
Tantalum - 10% Tungsten All Specimens Axial	3/8	NSWC	C104	None	20	19.08	6.39
	3/8	NSWC	C105	None	20	17.32	6.35
	3/8	NSWC	C106	None	20	19.08	6.39
	1/2	NSWC	T107	None		No Marks	6.36
	1/2	NSWC	T108	Photo		7.06	6.22
	3/8	NSWC	T109	Photo	20	4.18	6.31
	1/2	AEDC	T110	1" Ext.	HRB 101	No Marks	6.32
	3/8	TWCA	T152	Photo and 1/2" Ext.	HRB 92	20.14	5.05
	3/8	TWCA	T153	Photo and 1/2" Ext.	23	20.34	5.07
	1/4	FMGT	T200	1" Ext.	23	Many @ 5.08	6.30
300 Maraging Steel (Vascomax 300 CVM)	1 3/8" Dia. Bar End Marked 52 3461A Axial Trans- verse	NSWC	C111	None	51	19.04	6.36
		NSWC	C112	None		19.05	6.35
		NSWC	C113	None	52	19.02	6.39
		NSWC	T114	Photo		6.74	6.35
		NSWC	T115	Photo	51	7.30	6.34
		NSWC	C116	None	52	19.05	6.37
		NSWC	C117	None	52	19.06	6.29

Notes:

- NSWC -- Naval Surface Weapons Center, White Oak, MD.
TWCA -- Teledyne Wah Chang Albany.
AEDC -- Arnold Engineering Development Center, Arnold AF Station, TN.
FMGT -- Fansteel Metals. SMB tensile test grip test.
- T indicates tensile, C indicates compression test.
- All samples were strain gaged except T200. Photo indicates photographic coverage of scribed gage marks, 1/2" or 1" Ext. indicates extensometer.
- HRB and HRC -- Hardness on the Rockwell B and C scales.

IV. GRIP TESTS

The Ta-10W bar used for long rod penetrator phenomenology firings was 6.86 mm (.270 inch) diameter. For material properties tests, it was desirable to maintain the 6.35 mm reduced section diameter used in the bulk of the other tests. Mr. Victor Bates, Division Technical Manager, Fansteel Metals (a producer and potential supplier) suggested we use the technique that they use to obtain properties of full size bar. They use a 250 mm specimen length, reduce the diameter at the center about five hundredths of a millimetre, (0.002") using abrasive paper, mark the bar with fiducial marks every bar diameter, and pull the specimen to failure using checkered vee grips. SMB, TBD, did not have grips of precisely the design suggested, so it was not clear if the available grips would adequately hold the specimen without it pulling out. The alternative would be to use a 5.05 mm diameter reduced section specimen, with either 1/4-28 UNF or 1/4-32 UNEF threads on the end, but this was less desirable because the reduced size increases the experimental difficulties and the cost. In this case, this procedure also requires removing material in the specimen that is present in the real item, making the sample less representative. Mr. Bates kindly supplied us gratis with two 125 mm long specimens of fully work-hardened 6.35 mm diameter Ta-10W bar to investigate the various gripping methods. The use of checkered grips proved successful. While not the original goal of the testing, we were partially successful at obtaining additional stress-strain histories.

The material supplied was visually inspected and appears to be as-rolled material cleaned by etching, based on the frosted appearance and on seeing what must be flow lines -- wavy longitudinal striations not normally present on machined or abrasive finished material. The specimens were slightly out of round, running from 6.312 mm to 6.350 mm diameter. One end of one piece had a 0.08 mm deep gouge in it, so it was set aside for use as a threaded-end specimen if needed. Hardness was measured on freshly sanded ends on both specimens, and averaged HRC (Hardness on the Rockwell C scale) 23.0 with a standard deviation of 1.83. The reduced section diameter was produced on the grip test specimen by chucking it in a lathe and using #240 and then #320 grit 3M Tri-M-ite WETORDRY trademark silicon carbide paper, wet with a trichloroethane base coolant, to remove about 0.05 mm in the center. An 0.1 micrometre RMS finish was produced, with the lay circumferential. Two stripes with the same surface roughness but with the lay parallel to the long axis of the specimen were then created on diametrically opposite sides with #320 grit paper to provide contrast when scribed. Pairs of light transverse grooves were scribed on the specimen at nominal 0.200 inch intervals (5.08 mm), starting at an arbitrary location. The position of these marks was then measured with the same travelling microscope used to measure deformed length. Three diameters were measured and averaged at each gage mark to permit the computation of diametral strain.

The specimen was mounted in the Instron tensile test machine with the gage mark stripes oriented so as to be unmarred by the grips, with approximately 25 mm of material in each grip. This left approximately 6 mm of grip insert overhanging, which, combined with the tapering of the end grooves, formed a transition from full embossing of the specimen at its ends to just lightly embossing it at the grip ends. The grips were of a vee wedge design

with 1 mm pitch transverse grooved surfaces on each of the two vee faces of the insert. The grooves were similar to sharp crested buttress threads. The inserts bore no trade name, but were supplied with the testing machine and had "S-25" on the hidden end, and ".280-.500" on the other. Two layers of 3M Tri-M-ite WETORDRY trademark silicon carbide paper were wrapped on the zero end of the specimen. A one-inch clip extensometer was mounted on the specimen centered at 62 mm (2.45 inches) from the zero end and was connected to a chart recorder.

The test was run with the heads separating at 0.5 mm/min. The chart record was watched for evidence of slippage in the grips, but none was found, with the test terminating on specimen rupture. Figure 3 presents photographs of the two gripped ends of the specimens.

Necking occurred inside and very close to one extensometer knife edge. When the chart indicated a leveling out of load at near the expected yield, it was first interpreted as slippage in the grips, and the onset of necking was not noticed until it had obliterated a fiducial line. Thus, it was not possible to deduce whether the scribe mark initiated the necking. The test proceeded until the specimen broke. The break was nominally a cup and cone fracture, but was very unusual in that it was very clearly square. Possibly the change in lay of the surface finish around the circumference may have contributed to this, but close inspection of the ends suggest that this was almost certainly not the case. Since the processing history of the bar is unknown, additional speculation is fruitless. Figure 4 shows the broken specimen, and a close-up of the fractured ends.

The scribe marks were purposely closely spaced to provide detailed data about necking and incipient necking. The specimen was reduced by 1.5 percent of initial diameter at the smallest section. The ASTM standard test method recommends 1 percent, and this still was not adequate to precipitate necking there. The original profiles, radial strain, axial strain with the 0.2 inch and 1 inch gage lengths, initial and final areas, and per cent reduction in area are plotted in Figure 5. Note an incipient neck at about 20 mm from the zero end, indicated most clearly on the radial strain plot. Due to the lack of strain gage data, the elastic modulus and Poissons's ratio were not obtained. With necking occurring at one leg of the extensometer, detailed stress-strain data were likewise lost. However, the yield and ultimate strengths on this test were used in calculating the average values.

V. DATA REDUCTION PROCEDURES

The ASTM standard for tensile specimens sets the gage length at four times the diameter of the specimen. The distances between fiducial marks used in the photographic strain measuring technique were not in accord with this in most of these tests. Therefore, it was necessary to develop an expression that can infer what strains would have been measured had the proper gage length been used. Such an expression is developed below, based on the assumption that after the specimen has reached its ultimate strength the only elongation taking place will be between the two fiducial marks.

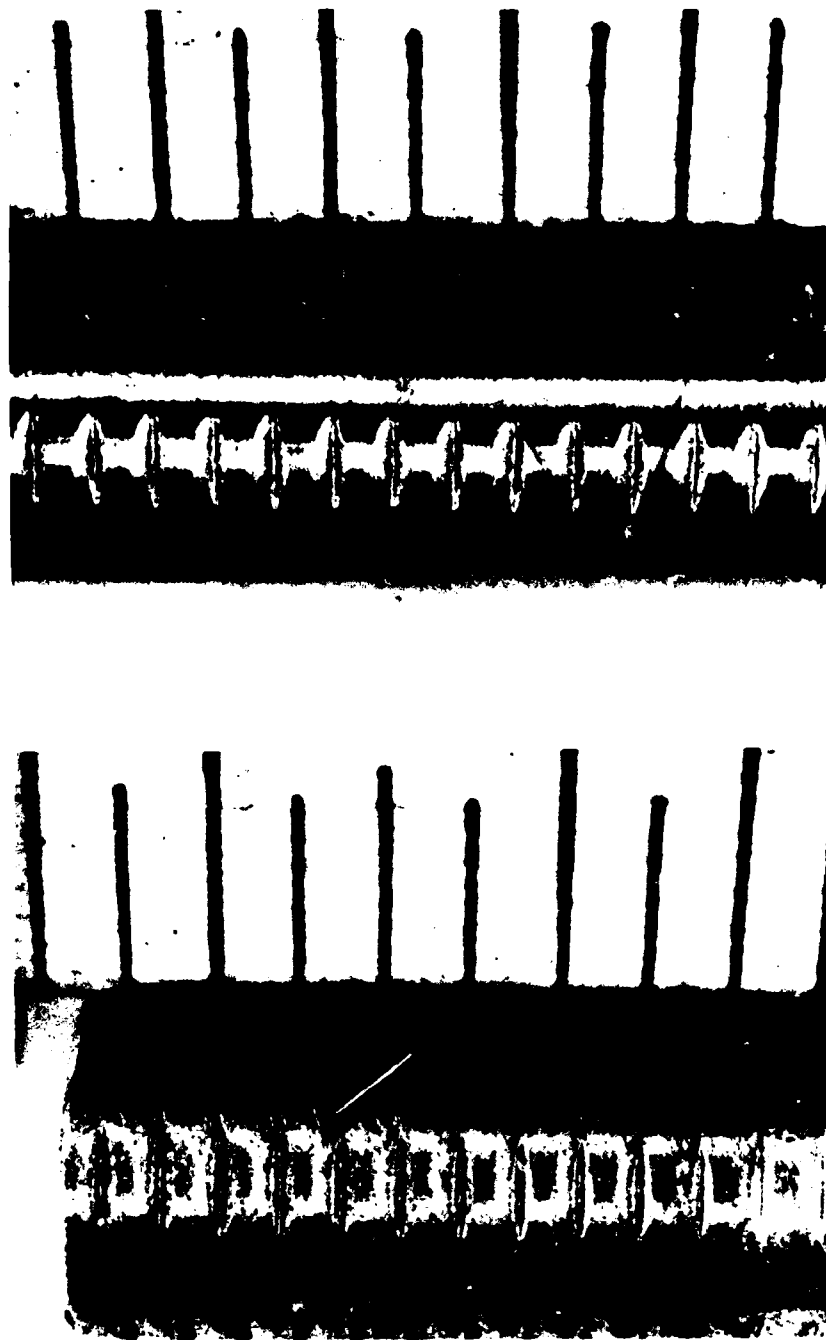


Figure 3. Embossing of 1/4 Inch Diameter Work-hardened Ta-10W Bar Specimen by Serrated Grips (Test T200). End in lower picture was wrapped with abrasive paper, while that in upper picture was bare. Scale graduations are 1/16".



Figure 4. Fractured Fully Work-hardened Ta-10W Grip Test Specimen (Test T200). Scale in upper photo graduated in inches and sixteenths. Lower photo shows unusual square break.

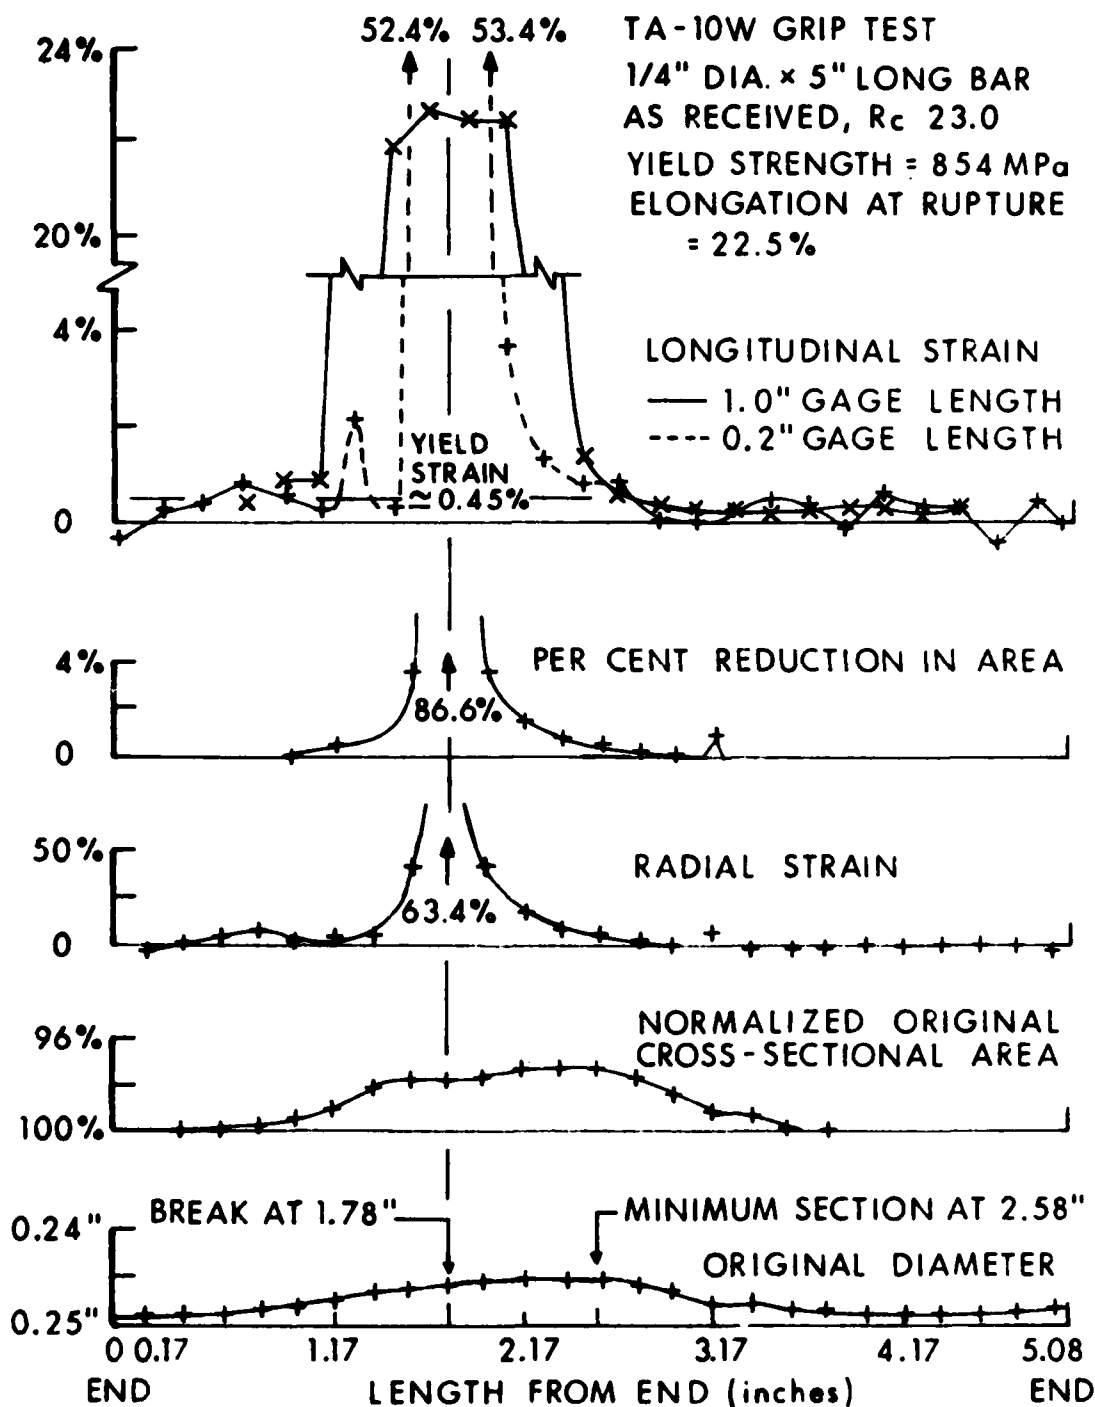


Figure 5. Data Plots from Grip Test of Fully Work-hardened Ta-10W Specimen (Test T200).

Given:

L_o = initial gage length between fiducial marks used in the experiment, and

L'_o = any other initial gage length for which an equivalent strain is sought.

Let $K = \frac{L'_o}{L_o}$.

Until necking occurs the strain is assumed to be uniform along the sample and is given by:

$$\epsilon = \epsilon' = \frac{L_o + \Delta L_o - L_o}{L_o} = \frac{\Delta L_o}{L_o}, \quad (1)$$

where ϵ = engineering strain as measured between the gage marks used,

ϵ' = engineering strain which would be measured between marks separated by gage length L'_o , and

ΔL_o = increase in length between fiducial marks used.

At the ultimate stress, define

$$\Delta L_u = \Delta L_o.$$

Beyond this point, necking is assumed to begin. Calling unit elongation at a point the strain, and the average unit elongation between gage marks the unit elongation, the strain and the unit elongation are no longer identical. There is very high strain in the necking area and little additional strain in the unnecked areas between the gage marks. Thus, different gage lengths result in different reported elongations. The unit elongation as seen by the fiducial marks would be equal to

$$\epsilon = \frac{\Delta L_u + \Delta L_n}{L_o}, \quad (2)$$

where L_n is the increase in distance between fiducial marks experienced during necking.

The equivalent unit elongation for marks initially separated by L'_o would be:

$$\epsilon' = \frac{\Delta L'_u + \Delta L_n}{L'_o} = \frac{K\Delta L_u + \Delta L_n}{KL_o}. \quad (3)$$

Solving for ΔL_n from Equation 2 and substituting it into Equation 3, one obtains:

$$\epsilon' = \frac{K-1}{K} \frac{\Delta L_u}{L_o} + \frac{\epsilon}{K}. \quad (4)$$

Therefore, by measuring the unit elongation between existing gage marks at the ultimate stress, one can infer the elongation that would be experienced between gage marks of a different spacing. Expression 4 was used to reduce the data from all tensile tests except T110 and T200 to a form consistent with values produced by tests using ASTM method E8-69 (ANS Z165.13-1971 [13]).

For the purposes of idealizing the stress-strain curves, a secant modulus was extracted from the data by averaging all the Young's moduli in each experimental run which were in a zone of mixed results. The beginning of this zone was selected as the first Young's modulus indicating full take-up on the tensile test machine. For strains up to about one half of the yield point, the moduli fluctuated from point to point, then began monotonically decreasing. The end of the zone was taken as the last modulus which was higher than its neighboring values. Each of these moduli were then averaged for each material in both tension and compression and this average modulus used for the Young's modulus in the idealized curves.

VI. RESULTS

The material properties are listed in Table 4. The yield strength is defined as that stress at which the specimens deviated 0.2 percent from proportionality of stress to strain. Young's modulus, yield strength and Poisson's ratio are determined from study of the foil strain gage records. The measured strains at rupture reported in Table 4 are in accordance with, or have been corrected by Expression 4 to that which would have been measured had the test been conducted in accordance with ASTM E8-69 [13]. There were no gage lines scribed on specimen T107, and therefore the strain at rupture was not measured. If the strain had been measured, it would have provided a comparison to that of T108, an identical specimen.

To estimate the strain at rupture for T107, the lengths of the post-test reduced sections of T107 and T108 were measured. Final strains were then calculated based on the changes in lengths of the reduced sections. The results for both tests were similar. Hence, it was assumed that the length of the reduced section at ultimate load for T107 would be approximated by that of T108, permitting expression (4) to be used to estimate the load at rupture for a standard gage length. For this calculation,

$$K = \frac{25.4 \text{ mm}}{38.1 \text{ mm}}, \quad \Delta L_u = 7.62 \text{ mm}, \quad \text{and} \quad \epsilon = 27.6\%,$$

with the result that the final strain at rupture for T107 would be 31.4%.

The tantalum alloy specimens were extremely ductile and exhibited considerable plastic work outside the four diameter zone in which necking is presumed to occur, which violates the assumptions used to derive Expression 4. Hence, the estimates of stain at rupture for this tantalum alloy obtained from the overall length of the reduced section are less believable than those estimated from gage marks. Comparing strains estimated in this fashion with

those corrected from non-standard gage marks provides a check on Expression 4. The details of the corrections to strain at rupture are reported in Table 5. The stress and strain data from photographic or extensometer records for tests T108 thru T110 and T114 and T115 are presented in Appendix Tables A1 and A2.

Table 4. Measured Material Properties

Material	Test Number	Young's Modulus (GPa)	Yield Strength (MPa)	Ultimate Strength (MPa)	Poisson's Ratio	Strain at Rupture (Percent)
Tantalum - 10% Tungsten Fully Annealed	C104	Results discarded -- excessive specimen bending				
	C105	198.20	460		.316	
	C106	197.04	462		.320	
	T107	192.31	450		.318	31.0 ^a
	T108	193.55	475	578	.322	35.9 ^b
	T109	191.69	462	569	.321	19.9 ^b
	T152	191.39	440	547	.330	41.2 ^c
	T110	188.68	855	856	.331	20.6
	T153	202.53	824	870	.328	16.6 ^c
	T200		854	859		22.5
300 Maraging Steel Solution Heat Treated	C111	199.14	2100		.300	
	C112	199.11	2100		.296	
	C113	200.44	2078		.298	
	T114	188.37	1977	2021	.310	12.0 ^b
	T115	187.83	1980	2023	.305	8.0 ^b
	C116	194.00	2160		.296	
	C117	186.67	2160		.288	

Notes:

- a. Inferred from post-test examination.
- b. Inferred from data from tests with non-standard gage lengths.
- c. Average of photo and 1/2 inch extensometer corrected to 1 inch.

Table 5. Measured (Photographic) and Corrected Engineering Strain at Rupture

Material	Test	Initial Gage Length	Initial Reduced Section Length	Gage or R S Length at Max Load (Ultimate)	Final or R S Gage Length	Engineering Strain at Ultimate Strength	Uncorrected Engineering Strain at Rupture	Engineering Strain at Rupture Inferred from Expression 4
		(mm)	(mm)	(mm)	(mm)	(percent)	(percent)	(percent)
Ta-10W	T107		38.10		48.62	20.0	27.6	31.4
Ta-10W	T108	7.06		8.48	12.50	20.0	77.0	35.9
			38.10	45.72	48.15	20.0	26.3	29.5
Ta-10W	T109	4.18		4.86	5.791	16.3	38.7	19.9
300M	T114	6.74		7.01	9.07	3.9	34.5	12.0
300M	T115	7.30		7.41	9.64	1.5	32.0	8.0

There were two classes of Ta-10W materials tested: fully annealed and fully work hardened. For the fully annealed material, Figure 6 presents engineering stress versus engineering strain in tension, to rupture, as measured via the photographic technique and calculated using expression (4), for tests T108 and T109. Note the extreme variation in elongation to rupture between the two samples. A stress-strain curve for the average of tests T107 thru T109, out to 7 percent strain, as measured by foil resistance strain gages, is presented in Figure 7. The error bands indicate plus and minus one standard deviation in the stress. Figure 8 presents engineering stress versus engineering strain for annealed Ta-10W in compression for test C105. The corresponding curve for a duplicate test, C106, deviated from that of C105 by less than 0.1 percent. For the fully work hardened material, Figure 9 presents an engineering stress versus engineering strain curve in tension, to rupture, for test T110.

For the maraging steel, Figure 10 presents a plot of engineering stress versus engineering strain, while Figure 11 replots the data as true stress versus true strain. The data are from test T115, with the strain measured from the photographic record and corrected as if the proper gage length had been used. True stress is defined as the intensity of load per unit of actual area, and is given by reference 16 as:

$$\epsilon_x = 2 \ln \frac{D_o}{D_f},$$

where D_o is the original and D_f is the final diameter, as determined photographically. Test T114 was a duplicate of T115, and the resulting curves are essentially identical. Figure 12 is the plot of the average engineering stress versus engineering strain for maraging steel in compression. Again, the error bands are at plus and minus one standard deviation. Figures 13 and 14 are photographs of the fractured specimens from all of the tensile tests except the grip test, T200, (shown earlier in Figure 4). Note that the ductility of the tantalum alloy is so extreme that it appears impossible to determine which specimens were fully work hardened and which were fully annealed from looking at the fractured tensile specimens.

The tantalum proved much more ductile than originally expected, and did not mimic the ballistic behavior of tungsten and uranium alloys. Increasing the reduction in area during the final rolling decreased the ratio of yield to ultimate strengths without significantly decreasing the ductility. The unexpectedly high ductility was attributed to the cleanliness of the product resulting from vacuum electric melting. The only viable approach to reducing the elongation appeared to be intentionally adding back embrittling agents in custom production, so further efforts at modifying properties were abandoned.

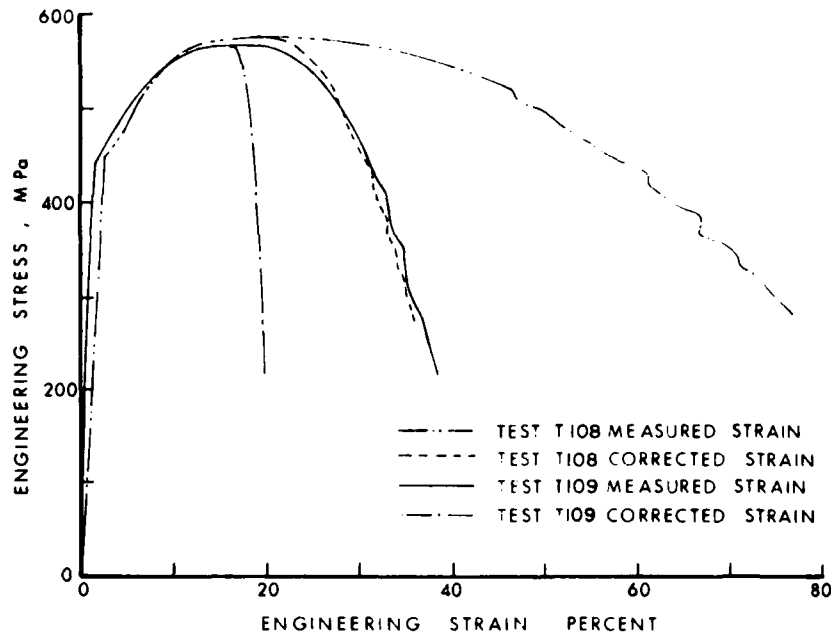


Figure 6. Individual Measured and Corrected Engineering Stress versus Engineering Strain Curves, to Rupture, for Annealed Ta-10W in Tension, from Tests T108 and T109.

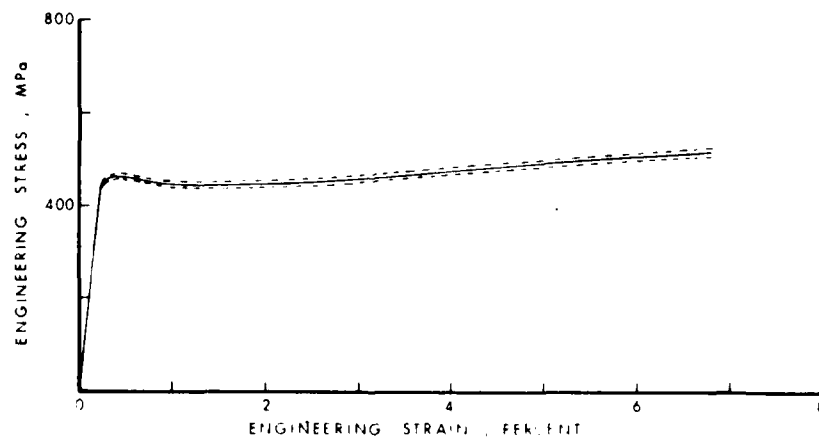


Figure 7. Average Engineering Stress versus Engineering Strain, to 7% Strain, for Annealed Ta-10W in Tension, Tests T107 thru T109.

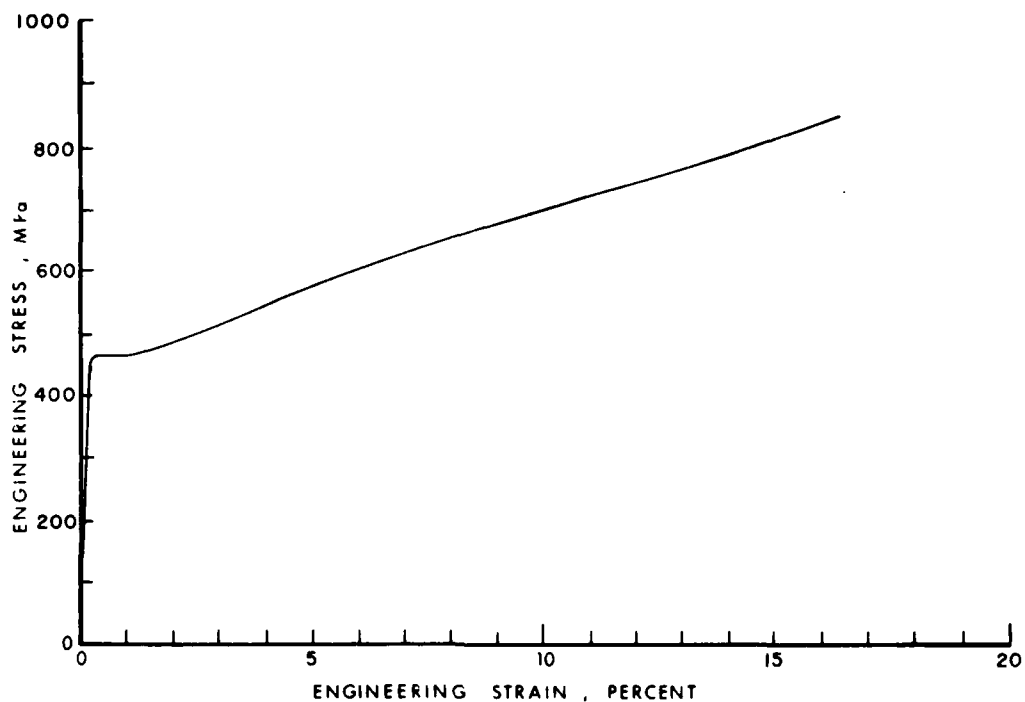


Figure 8. Engineering Stress versus Engineering Strain for Annealed Ta-10W in Compression from Test C105. The data from compression test C106 deviated less than 1/2% from this curve.

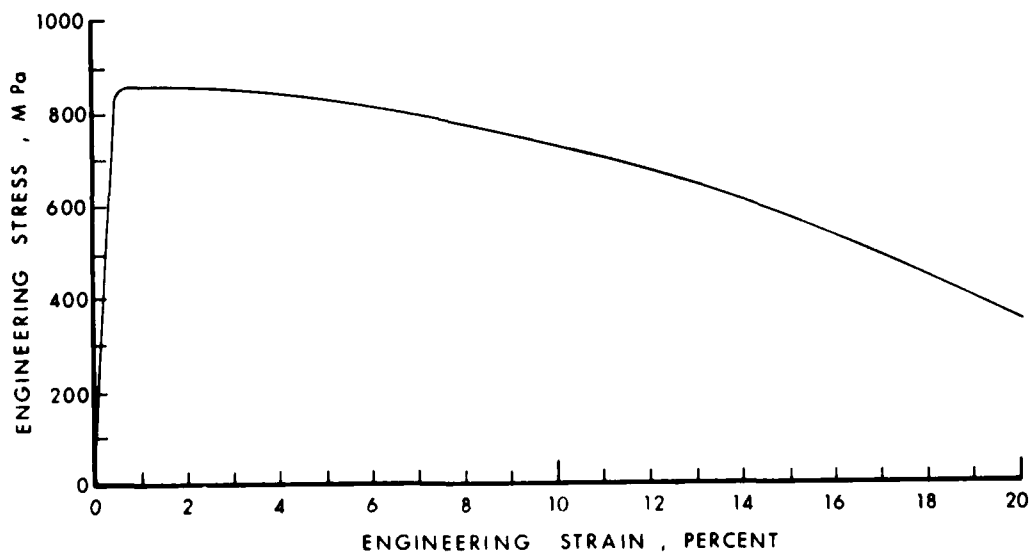


Figure 9. Engineering Stress versus Engineering Strain, to Rupture, for Fully Work-hardened Ta-10W in Tension, from Test T110.

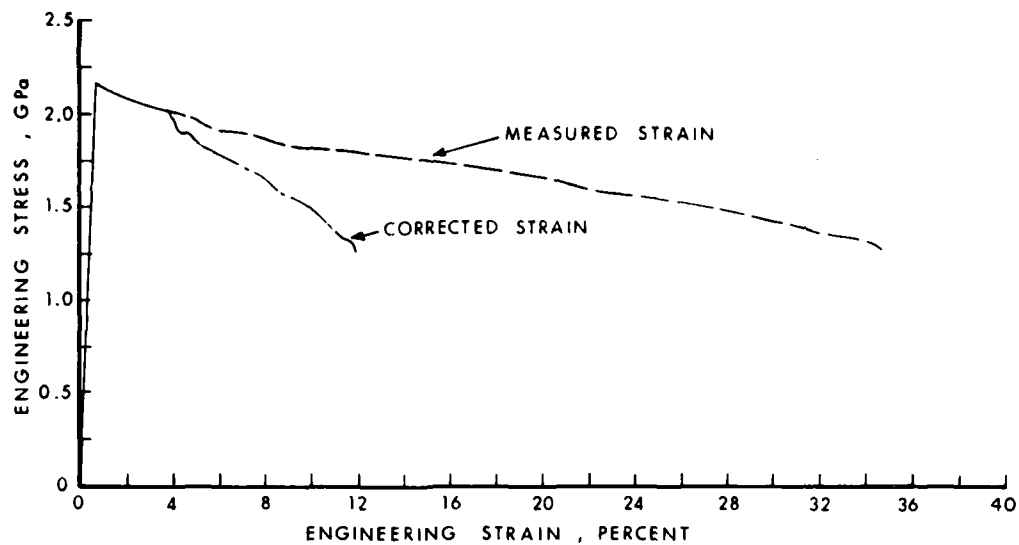


Figure 10. Measured and Corrected Engineering Stress versus Engineering Strain, to Rupture, for Precipitation Hardened 300 Maraging Steel in Tension, from Test T115.

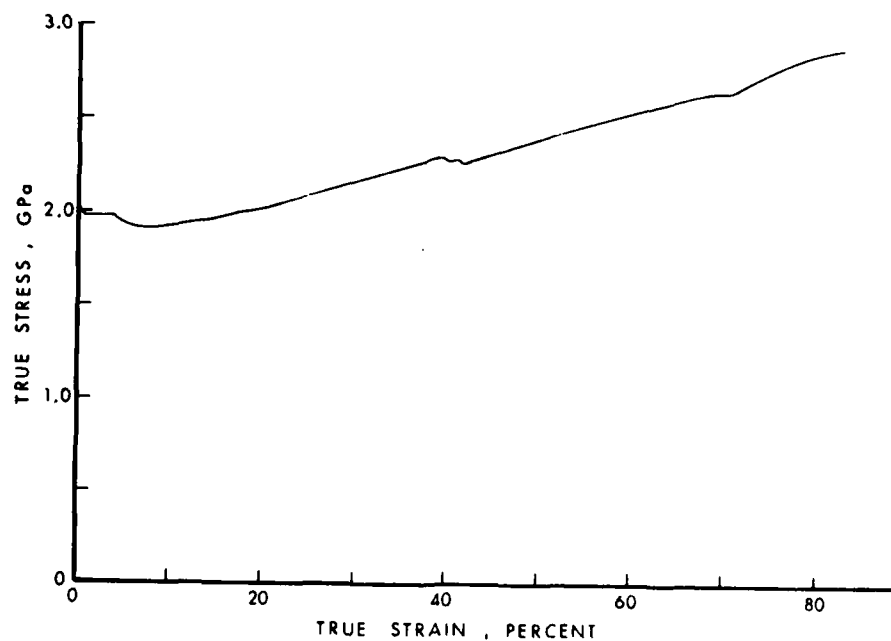


Figure 11. True Stress versus True Strain, to Rupture, for Precipitation Hardened 300 Maraging Steel in Tension, from Test T115.

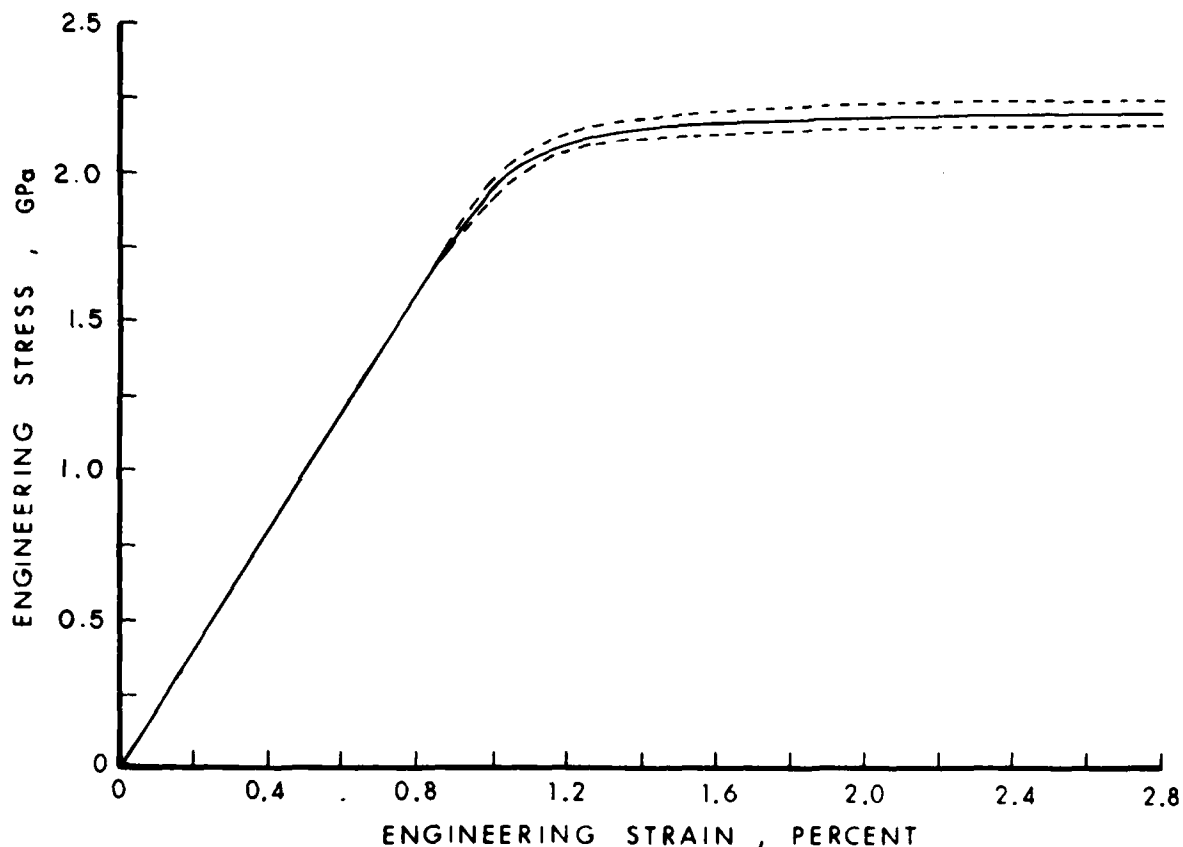


Figure 12. Average Engineering Stress versus Engineering Strain for Precipitation Hardened 300 Maraging Steel in Compression from Tests C111 thru C113.

VII. ACKNOWLEDGEMENTS

The authors wish to acknowledge a number of individuals and organizations for their assistance with the project. Len Crogan of the Naval Surface Weapons Center in White Oak, Maryland, supplied sample materials and preliminary tensile test results of materials from penetrators fired at their Pressurized Ballistic Range 3. Randall Watt of Arnold Research Organization, the operating contractor of the US Air Force System Command's Arnold Engineering Development Center in Tennessee supplied samples and certifications of material from penetrators fired at their von Karman Gas Dynamics Facilities' Hyperballistic Range G. Mr. Victor Bates of the Metals Division of Fansteel Metals, Inc., Mr. Robert Marsh of Teledyne Wah-Chang Albany, Mr. Ronald Fedora of Norton Metals Division, and Mr. Donald L. Groves of Kawecki-Berylco Company supplied technical advice in connection with the procurement of controlled-elongation tantalum-tungsten alloys. Finally, the authors wish to thank Jeff Sakai, formerly of the Fragmentation Branch, TBD, BRL, for his valuable metallurgical advice, and Mr. William Donovan of the Mechanics and Structures Branch, Interior Ballistics Division, BRL, for his prompt and thorough review of the report manuscript.

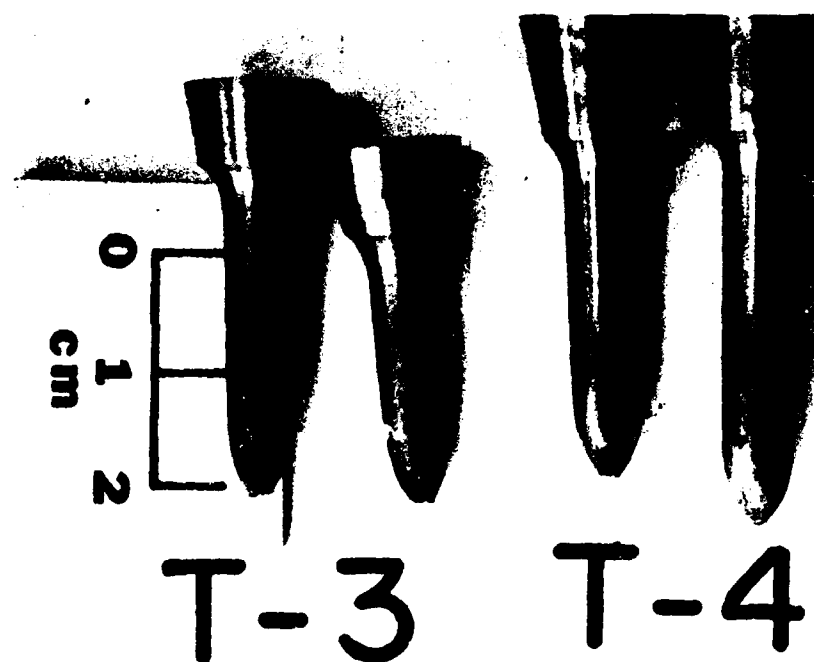


Figure 13. Post-test Ta-10W Tensile Specimens. T-3 is from test T108, T-4 from T110, T-2 from T107, and T-1 from T109.

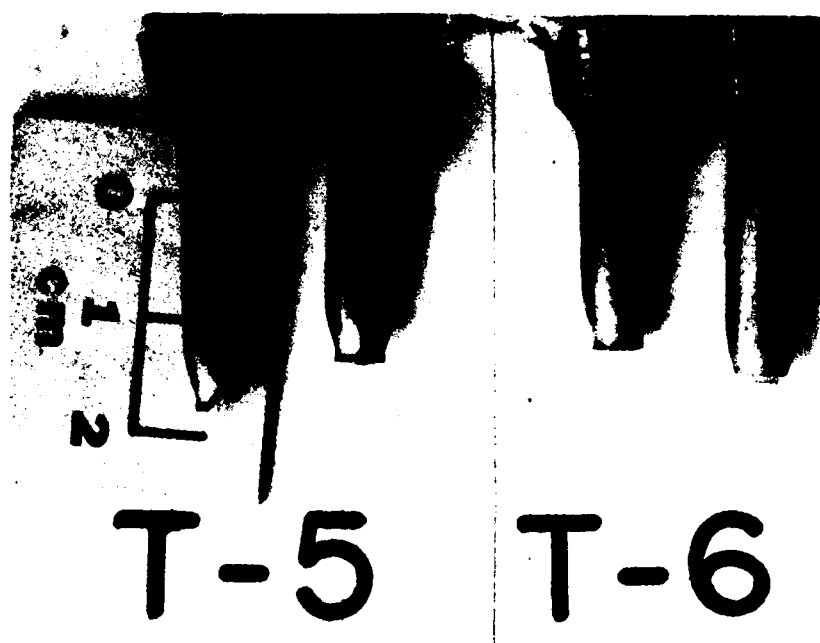
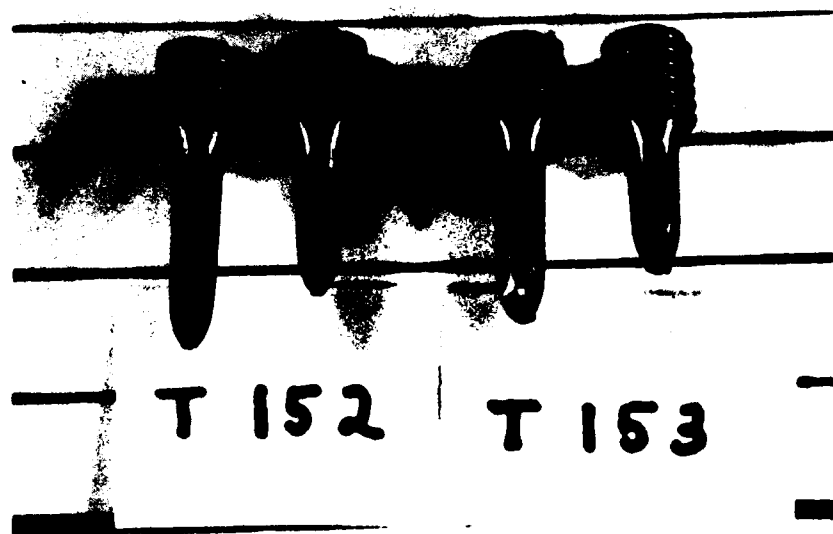


Figure 14. Post-Test Ta-10W and 300 Maraging Steel Tensile Specimens. The Ta-10W specimens from T152 and T153 are photographed inclined against a half-inch grid. The lower specimens are maraging steel, and are from tests T114 (T-5) and T115 (T-6).

REFERENCES

1. Murray, Jr., E.A., and Suckling, J.H., "Quasi-static Compression Stress - Strain Curves -- I, 1066 Steel," BRL Memorandum Report 2399, Ballistic Research Laboratories, Aberdeen Proving Ground, MD, July 1974, AD 922704L.
2. Murray, Jr., E.A., "Quasi-static Compression Stress - Strain Curves -- II, 7039 Aluminum," BRL Memorandum Report 2589, Ballistic Research Laboratories, Aberdeen Proving Ground, MD, February 1976, AD B009646L.
3. Benck, R.F., and Murray, Jr., E.A., "Quasi-static Compression Stress - Strain Curves -- III, 5083-H131 Aluminum," BRL Memorandum Report 2480, Ballistic Research Laboratories, Aberdeen Proving Ground, MD, May 1975, AD B004159L.
4. Benck, R.F., Filbey, G.L., and Murray, Jr., E.A., "Quasi-static Compression Stress - Strain Curves -- IV, 2024-T3510 and 6061-T6 Aluminum Alloys," BRL Memorandum Report 2655, Ballistic Research Laboratories, Aberdeen Proving Ground, MD, August 1976, AD B013221L.
5. Benck, R.F., and Filbey, Jr., G.L., "Elastic Constants of Aluminum Alloys, 2024-T3510, 5083-H131 and 7039-T64 as Measured by a Sonic Technique," BRL Memorandum Report 2649, Ballistic Research Laboratories, Aberdeen Proving Ground, August 1976, AD B012953L.
6. Benck, R.F., and DiBerardo, D.A., "Quasi-static Tensile Stress - Strain Curves -- I, 2024-T3510 Aluminum," BRL Memorandum Report 2587, Ballistic Research Laboratories, Aberdeen Proving Ground, MD, February 1976, AD B009639L.
7. Benck, R.F., and Robitaille, J., "Tensile Stress - Strain Curves -- II Rolled Homogeneous Armor," BRL Memorandum Report 2703, Ballistic Research Laboratories, Aberdeen Proving Ground, MD, November 1976, AD B016015L.
8. Benck, R.F., and Robitaille, J., "Tensile Stress - Strain Curves -- III Rolled Homogeneous Armor at Strain Rate of 0.42 s^{-1} ," BRL Memorandum Report 2760, Ballistic Research Laboratories, Aberdeen Proving Ground, MD, June 1977, AD A014560L.
9. Wolf, J., and Brown, Jr., W.F., Ed., "Ta-10%W, Material Code 5402," Aerospace Structural Metals Handbook, 1976 Edition, Volume IV, AFML-TR-68-115, Mechanical Properties Data Center, Belfour Stulen, Inc., Traverse City, MI 49684, 1975, pp. 1-14, AD 737973.
10. Small, Louis, "Part I, Practice," Hardness -- Theory and Practice, 1960, Service Diamond Tool Co., Ferndale, MI 48220, pp. 483-484.
11. Application Data for Nickel Maraging Steels, VASCO Corporation, Latrobe, PA 15650, 1968.

12. Moore, T.D., Ed., Structural Alloys Handbook, Volume 2, 1976 Edition, Mechanical Properties Data Center, Belfour Stulen, Inc., Traverse City, MI 49684, Appendix C, pp. 1-7.
13. ASTM Committee E-28 on Mechanical Testing, ANS Z165.13-1971, "Standard Methods of Tension Testing of Metallic Materials," American National Standards Institute, 1969.
14. ASTM Committee E-28 on Mechanical Testing, ANS Z115.16-1973, "Standard Methods of Compression Testing of Metallic Materials at Room Temperature," American National Standards Institute, 1969.
15. ASTM Committee E-28 on Mechanical Testing, ANS Z115.6-1967, "Standard Methods of Testing for Rockwell Hardness and Rockwell Superficial Hardness of Metallic Materials," American National Standards Institute, 1967.
16. Hetenyi, M., Ed., Handbook of Experimental Stress Analysis, John Wiley and Sons, Inc., New York, NY, 1950.
17. Hines, William W., and Montgomery, Douglas D., Probability and Statistics in Engineering and Management Science, Ronald Press, New York, 1972.

APPENDIX

Table A1. Engineering Strain and Engineering Stress
for Ta-10W Specimens, Measured on
Tensile Tests T108 thru T110

Test T108		Test T109		Test T110			
Strain (Photo- graphic)	Stress	Strain (Photo- graphic)	Stress	Strain (Exten- someter)	Stress	Strain (Exten- someter)	Stress
(percent)	(MPa)	(percent)	(MPa)	(percent)	(MPa)	(percent)	(MPa)
0.	0.	0.	0.	0.	0.		
0.67	96.7	.18	158.6	0.003	42.0	3.34	850.3
2.70	453.0	1.54	445.7	0.007	61.7	3.67	846.6
2.85	454.0	3.76	479.5	0.019	87.7	3.95	843.8
4.94	482.0	5.58	506.5	0.041	119.0	4.18	840.5
6.07	512.6	6.79	523.7	0.061	152.3	4.42	835.2
7.94	535.2	9.57	552.8	0.070	183.8	4.71	831.6
10.86	561.0	12.09	562.6	0.098	228.6	5.13	827.5
13.93	573.9	14.20	567.6	0.124	266.7	5.62	819.4
19.33	577.5	16.20	568.8	0.155	308.8	6.07	811.7
23.37	576.5	19.35	567.6	0.177	346.0	6.53	802.3
26.59	574.2	21.91	561.0	0.215	396.5	6.98	794.6
32.73	566.8	24.59	545.6	0.237	455.9	7.40	786.1
37.68	554.6	26.58	526.6	0.268	503.1	7.40	778.8
39.93	548.1	27.66	508.3	0.299	551.5	8.39	765.7
43.07	535.2	29.02	487.0	0.345	625.8	8.99	752.7
46.52	522.3	29.91	470.1	0.364	658.4	9.48	742.6
47.19	509.4	31.07	451.3	0.380	681.2	10.04	729.2
50.41	496.5	31.54	432.5	0.397	704.4	10.54	717.0
51.98	482.0	32.80	410.2	0.411	725.1	11.06	703.6
53.86	470.7	33.33	394.9	0.428	743.4	11.59	689.7
55.96	457.8	33.67	379.3	0.437	758.4	12.05	675.9
58.50	444.9	34.06	363.5	0.450	773.9	12.50	662.5
61.35	432.0	35.01	351.0	0.466	789.3	13.01	646.2
61.12	419.1	34.87	338.5	0.483	806.8	13.57	628.4
63.07	406.2	35.32	325.3	0.510	823.0	14.12	611.7
63.74	399.8	35.32	310.3	0.543	836.1	14.59	594.2
65.09	393.4	35.80	294.6	0.584	844.6	15.11	575.5
66.67	386.9	36.66	282.1	0.622	849.5	15.63	555.6
67.27	377.2	36.98	272.7	0.677	852.3	16.12	536.5
66.52	367.6	37.21	260.1	0.734	853.9	16.64	515.4
69.51	354.7	37.65	250.7	0.885	854.8	16.96	496.3
70.86	341.8	37.51	247.0	1.01	855.6	17.39	478.0
70.94	332.1	37.98	236.3	1.20	855.6	17.72	462.9
72.90	322.4	38.26	225.6	1.53	854.8	18.15	442.2
74.46	303.1	38.71	213.1	1.88	855.6	18.68	416.6
77.08	277.2			2.25	855.2	19.19	392.6
				2.69	853.9	19.67	366.6
				3.03	851.9	20.62	312.6

**Table A2. Engineering Strain and Engineering Stress for
300 Maraging Steel Specimens, Measured Photo-
graphically on Tensile Tests T114 and T115.**

Test T114			Test T115		
<u>Stress</u>	<u>Strain</u>	<u>Specimen</u>	<u>Stress</u>	<u>Strain</u>	<u>Specimen</u>
(GPa)	(percent)	Diameter (mm)	(GPa)	(percent)	Diameter (mm)
0.	0.	6.350	0.	0.	6.342
0.533	0.23	6.345	1.899	0.	6.342
1.833	0.70	6.340	2.040	1.59	6.342
2.019	3.89	6.238	2.029	2.45	6.342
1.966	5.29	6.203	1.967	3.75	6.327
1.941	5.44	6.172	1.931	6.42	6.284
1.920	5.83	6.132	1.899	7.00	6.215
1.895	7.62	6.152	1.869	7.51	6.210
1.865	8.32	6.116	1.836	8.81	6.190
1.833	9.49	6.071	1.792	11.70	6.152
1.827	10.11	5.984	1.766	12.49	6.116
1.783	13.06	5.519	1.757	12.92	6.078
1.743	15.55	5.484	1.725	14.37	5.994
1.709	17.34	5.357	1.693	15.02	5.916
1.678	19.36	5.220	1.677	15.23	5.809
1.641	20.76	5.128	1.646	16.68	5.730
1.603	21.77	5.047	1.616	17.83	5.491
1.571	23.56	5.001	1.583	18.70	5.344
1.532	25.97	4.854	1.553	19.85	5.217
1.494	27.92	4.818	1.532	20.07	5.202
1.409	30.33	4.696	1.519	20.94	5.174
1.387	31.49	4.580	1.494	21.44	5.159
1.365	31.73	4.488	1.472	22.09	4.986
1.319	34.14	4.366	1.377	28.01	4.625
1.269	34.76	4.346	1.361	28.95	4.575
			1.342	29.46	4.521
			1.315	30.40	4.468
			1.298	31.12	4.282
			1.266	31.98	4.194

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
1	Director Defense Nuclear Agency ATTN: SPAS (MAJ Douglas Apo) Arlington, VA 22209	10	Commander Naval Surface Weapons Center ATTN: Code K-22 J. Etheridge Code R-13: F. J. Zerilli K. Kim E. T. Toton M. J. Frankel Code R-32: Alexander Rozner Hampton de Jarnette Code U-11: J. R. Renzi R. S. Gross Code U-23: William Hinckley Silver Spring, MD 20903-5000
2	Commander US Army BMD Advanced Technology Center ATTN: BMDATC-M (Mr. P. Boyd) Mr. S. Brockway PO Box 1500 Huntsville, AL 35807		
1	Commander US Army R&D Center ATTN: SMCAR-SCM(D), (Dr. E. Bloore) Dover, NJ 07801		
2	Commander US Army Missile Command ATTN: Fran Wlodarski M. Morrow Redstone Arsenal, AL 35809	8	Commander Naval Weapons Center ATTN: Code 3181: John Morrow Code 3261: Mr. C. Johnson Mr. T. Zulkoski Code 3171: Mr. B. Galloway Code 3831: Mr. M. Backman Dr. O. E. R. Heimdahl Dr. Kenneth Graham Code 3894: C. Lorenzen China Lake, CA 93555
2	Director US Army Material Technology Laboratory ATTN: J. Mescall R. Shea Watertown, MA 02172		
2	Commander US Army Research Office ATTN: Dr. E. Saibel Dr. G. Mayer PO Box 12211 Research Triangle Park NC 27709		
1	Commander and Director David W. Taylor Naval Ship R&D Center ATTN: Code 1740.4, (R. A. Gramm) Bethesda, MD 20084	3	Superintendent Naval Postgraduate School ATTN: Library Director Dr. Gilbert Kinney Dr. Richard Reinhardt Monterey, CA 93940
		3	ADTC/DLJW: LT K. Ols, LT J. Flores, Mr. W. Cook Eglin AFB, FL 32542

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
1	ADTC/DLYV (Mr. J. Collins) Eglin AFB, FL 32542	2	Sandia National Laboratories ATTN: Dr. L. D. Bertholf Dr. D. Bammann Livermore, CA 94550
2	AFOSR: W. J. Walker Dr. M. Zimmer Bolling Air Force Base Washington, DC 20332	6	Strategic Defense Initiative Organization 1717 H Street, NW ATTN: Dr. Gerold Jones, Rm 416 Dr. James Ionson, Rm 326 COL M. O'Neill, Rm 734 Dr. L. Marquet, Rm 331 Mr. John Gardner, Rm 332 COL George Hess, Rm 449 Washington, DC 20006
1	AFWAL/MLLN Metals & Ceramics Div ATTN: Dr. T. Nicholas Wright-Patterson AFB, OH 45433	1	AVCO Systems Division 201 Lowell Street ATTN: Dr. Reinecke Wilmington, MA 01803
2	Arnold Engineering Development Center VKF Range G Building Randall Watt N. Weinburg Arnold AF Station, TN 37389	1	Battelle Columbus Laboratories 505 King Avenue ATTN: G. Throner Columbus, OH 43201
4	Lawrence Livermore National Laboratory PO Box 808 ATTN: Technical Library Dr. G. Goudreau Dr. J. O. Hallquist Dr. M. L. Wilkins Livermore, CA 94550	4	Boeing Aerospace Company ATTN: Mr. R. G. Blaisdell (M.S. 40-25) Dr. N. A. Armstrong, C. J. Artura (M.S. 8C-23) Dr. B. J. Henderson (M.S. 43-12) Seattle, WA 98124
7	Los Alamos National Laboratory PO Box 1663 ATTN: Tech Library Dr. J. Dienes Scott Hill Dr. R. Karpp Dr. C. Mader John Meier Dr. J. Taylor Los Alamos, NM 87545	1	Computer Code Con- sultants, Inc. 1680 Camino Redondo ATTN: Dr. Wally Johnson Los Alamos, NM 87544
6	Sandia National Laboratories ATTN: L. Davison M. J. Forrestal Dr. W. Herrmann M. Kipp M. J. Sagartz A. L. Stevens Albuquerque, NM 87115	2	Dupont Experimental Labs ATTN: Mr. J. Lupton Dr. C. Zweben 1007 Market Street Wilmington DE 19898

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
4	Fansteel Inc., Metals Division 1 Tantalum Place ATTN: Victor T. Bates (2 Cys) E. Jenstrom A. Bradlav North Chicago, IL 60064	1	Kawecki-Berylco 220 E 42 St. New York, NY 10017
1	Fansteel Inc., Metals Division PO Box 277 ATTN: Jack Klink Joppa, MD 21085	1	Lockheed Missiles and and Space Co. PO Box 3504 ATTN: Org 8320, Bldg 157-3W, Robert Weinheimer Sunnyvale, CA 94088-3504
4	FMC Corporation Ordnance Engineering Division ATTN: Claude Braafladt Robert Burt Neil Kennedy Anthony Lee PO Box 1201 San Jose, CA 95108	1	Materials Research Laboratory, Inc. 1 Science Road Glenwood, IL 60427
4	Ford Aerospace and Communications Co. Ford Road, PO Box A ATTN: L. K. Goodwin C. E. Blair E. R. Mijares R. C. Morenus Newport Beach, CA 92660	1	N R C Co. 45 Industrial Place ATTN: Zane Laycock Newton, MA 02164
1	General Dynamics PO Box 2507 ATTN: J. H. Cuadros Pomona, CA 91745	2	Orlando Technology, Inc. PO Box 855 ATTN: Mr. J. Osborn Mr. D. Matuska Shalimar, FL 32579
3	Honeywell, Inc. 5901 South County Road 18 ATTN: Ms. Peggy Anderson Dr. C. Candland Dr. G. Johnson Edina, MN 55436	3	Schlumberger Well Services Perforating Center ATTN: J. Brookman J. E. Brooks Dr. C. Aseltine PO Box A Rosharon, TX 77543
1	Kawecki-Berylco PO Box 1462 ATTN: Donald L. Groves Reading, PA 19603	4	Southwest Research Institute Dept. of Mechanical Sciences ATTN: Dr. U. Lindholm Dr. R. White Dr. M. F. Kanninen Dr. C. Anderson 8500 Culebra Road San Antonio, TX 78228

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
4	SRI International 333 Ravenswood Avenue ATTN: Dr. L. Seaman Dr. L. Curran Dr. D. Shockey Dr. A. L. Florence Menlo Park, CA 94025	4	Cornell University Department of Theoretical and Applied Mechanics ATTN: Dean E. Cranch Professor G. Ludford Professor D. Robinson Professor Y-H. Pai Ithaca, NY 14850
1	Systems, Science and Software PO Box 1620 ATTN: Dr. R. Sedgwick La Jolla, CA 92038	2	Drexel University Department of Mechanical Engr. ATTN: Dr. P. C. Chou Dr. F. K. Tsou 32 and Chestnut Streets Philadelphia, PA 19104
1	Teledyne Vasco Latrobe, PA 15650	3	New Mexico Institute of Mining and Technology ATTN: Lamar Kempton Dr. Max Bloom Dr. M. A. Meyer Socorro, NM 87801
1	Teledyne Wah-Chang Albany PO Box 460 ATTN: R. Marsh Albany, NY 97371	2	Johns Hopkins University 34 and Charles Streets ATTN: Dr. J. Bell Dr. R. Green Baltimore, MD 21218
1	US Steel Corporation Research Center 125 Jamison Center Monroeville, PA 15146	2	Lehigh University Center for the Application of Mathematics ATTN: Dr. E. Varley Dr. R. Rivlin Bethlehem, PA 18015
2	Vought Corporation PO Box 225907 ATTN: Dr. G. Hough Dr. Paul M. Kenner Dallas, TX 75265	2	Massachusetts Institute of Technology 77 Massachusetts Avenue ATTN: Dr. R. Probststein Dr. J. Dugundji Cambridge, MA 02139
2	Brown University Division of Engineering ATTN: Professor R. J. Clifton Professor P. Symonds Providence, RI 02192		
2	California Institute of Tech Division of Engineering and Applied Science ATTN: Dr. J. Miklowitz Dr. E. Sternberg Pasadena, CA 91102		

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
2	Princeton University Forrestal Research Center Aeronautical Engineering Lab ATTN: Dr. S. Lam Dr. A. Eringen Princeton, NJ 08540	2	University of Maryland Department of Mechanical Engineering ATTN: Professor Y. Yang Dr. J. Dally College Park, MD 20742
2	University of California College of Engineering ATTN: Prof. W. Goldsmith Dr. A. G. Evans Berkeley, CA 94720	1	University of Minnesota Department of Engineering Mechanics ATTN: Dr. R. Fosdick Minneapolis, MN 55455
1	University of Denver Denver Research Institute ATTN: Mr. R. F. Recht 2390 S. University Blvd. Denver, CO 80210	2	University of Texas Department of Engineering Mechanics ATTN: Dr. C. H. Yew Professor Ripperger Austin, TX 78712
2	University of Florida Department of Engineering Sciences ATTN: Dr. L. F. Malvern Dr. C. Scimmarella Gainesville, FL 32601	1	University of Washington Department of Mechanical Engineering ATTN: Professor Chalupnik Seattle, WA 98105
1	University of Illinois at Chicago Circle College of Engineering Department of Materials Engineering ATTN: Professor A. Shultz PO Box 4348 Chicago, IL 60680	2	Washington State University Department of Physics ATTN: Dr. G. E. Duvall R. W. Fowler Pullman, WA 99163
1	University of Illinois Department of Theoretical and Applied Mechanics ATTN: Dr. D. Carlson Urbana, IL 61801	2	Yale University 400 Temple Street ATTN: Dr. B. Chu Dr. E. Onat New Haven, CT 96520
2	University of Kentucky Department of Engineering Mechanics ATTN: Dr. M. Beatty Professor P. Gillis Lexington, KY 40506	1	The National Materials Property Data Network, Inc. ATTN: J. Gilbert Kaufman c/o MPC 14 Floor 345 E 47 Street New York, NY 10017

<u>Copies</u>	<u>Organization</u>	<u>Copies</u>	<u>Organization</u>
12	Administrator Defense Technical Info Center ATTN: DTIC-DDA Cameron Station Alexandria, VA 22304-6145	1	Commander U.S. Army Communications- Electronics Command ATTN: AMSEL-ED Fort Monmouth, NJ 07703
1	HQDA DAMA-ART-M Washington, D.C. 20310	1	Commander ERADCOM Technical Library ATTN: DELSD-L (Reports Section) Fort Monmouth, NJ 07703-5301
1	Commander U.S. Army Materiel Command ATTN: AMCDRA-ST 5001 Eisenhower Avenue Alexandria, VA 22333-0001	1	Commander U.S. Army Missile Command Research, Development & Engin- eering Center ATTN: AMSMI-RD Redstone Arsenal, AL 35898
1	Commander Armament R&D Center U.S. Army AMCCOM ATTN: SMCAR-TSS Dover, NJ 07801	1	Director U.S. Army Missile & Space Intelligence Center ATTN: AIAMS-YDL Redstone Arsenal, AL 35898-5500
1	Commander Armament R&D Center U.S. Army AMCCOM ATTN: SMCAR-TDC Dover, NJ 07801	1	Commander U.S. Army Tank Automotive Cmd ATTN: AMSTA-TSL Warren, MI 48397-5000
1	Director Benet Weapons Laboratory Armament R&D Center U.S. Army AMCCOM ATTN: SMCAR-LCB-TL Watervliet, NY 12189	1	Director U.S. Army TRADOC Systems Analysis Activity ATTN: ATAA-SL White Sands Missile Range, NM 88002
1	Commander U.S. Army Armament, Munitions and Chemical Command ATTN: SMCAR-ESF-L Rock Island, IL 61299	1	Commandant U.S. Army Infantry School ATTN: ATSH-CD-CSO-OR Fort Benning, GA 31905
1	Commander U.S. Army Aviation Research and Development Command ATTN: AMSAV-E 4300 Goodfellow Blvd St. Louis, MO 63120	1	Commander U.S. Army Development and Employ- ment Agency ATTN: MODE-TED-SAB Fort Lewis, WA 98433
1	Director U.S. Army Air Mobility Research and Development Laboratory Ames Research Center Moffett Field, CA 94035	1	AFWL/SUL Kirtland AFB, NM 87117
		1	Air Force Armament Laboratory ATTN: AFATL/DLODL Eglin AFB, FL 32542-5000

CopiesOrganizationABERDEEN PROVING GROUND

10

Central Intelligence Agency
Office of Central Reference
Dissemination Branch
Room GE-47 HQS
Washington, D.C. 20502

Dir, USAMSAA

ATTN: AMXSY-D
AMXSY-MP, H. Cohen

Cdr, USATECOM

ATTN: AMSTE-TO-F

Cdr, CRDC, AMCCOM

ATTN: SMCCR-RSP-A
SMCCR-MU
SMCCR-SPS-IL

USER EVALUATION SHEET/CHANGE OF ADDRESS

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. BRL Report Number _____ Date of Report _____
2. Date Report Received _____
3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) _____

4. How specifically, is the report being used? (Information source, design data, procedure, source of ideas, etc.) _____

5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided or efficiencies achieved, etc? If so, please elaborate. _____

6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) _____

CURRENT ADDRESS	_____
	Name

	Organization

	Address

	City, State, Zip

7. If indicating a Change of Address or Address Correction, please provide the New or Correct Address in Block 6 above and the Old or Incorrect address below.

OLD ADDRESS	_____
	Name

	Organization

	Address

	City, State, Zip

(Remove this sheet along the perforation, fold as indicated, staple or tape closed, and mail.)

----- FOLD HERE -----

Director
U.S. Army Ballistic Research Laboratory
ATTN: SLCBR-DD-T
Aberdeen Proving Ground, MD 21005-5066




NO POSTAGE
NECESSARY
IF MAILED
IN THE
UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE, \$300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO 12062 WASHINGTON, DC
POSTAGE WILL BE PAID BY DEPARTMENT OF THE ARMY

Director
U.S. Army Ballistic Research Laboratory
ATTN: SLCBR-DD-T
Aberdeen Proving Ground, MD 21005-9989

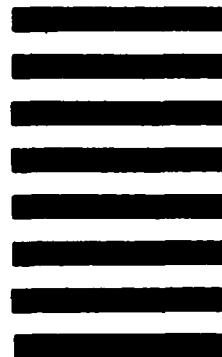

----- FOLD HERE -----