

HD-A186 296

ELECTROCATALYTIC REDUCTION OF MOLECULAR OXYGEN BY
MONONUCLEAR AND BINUCLE (U) YORK UNIV DOWNSVIEW
(ONTARIO) DEPT OF CHEMISTRY M R HEMPSTEAD ET AL


1/1


UNCLASSIFIED

AUG 87 TR-17 \$N00014-84-G-0201

F/G 7/3

NL

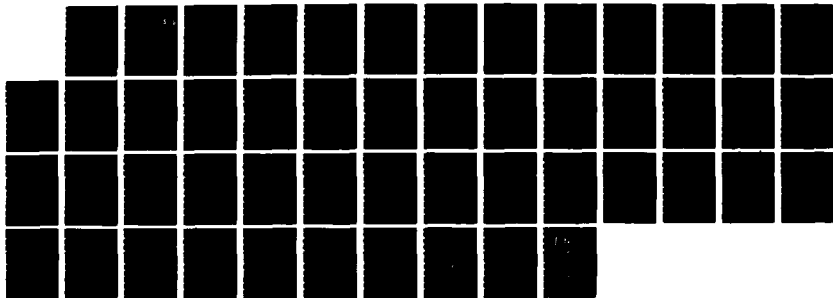

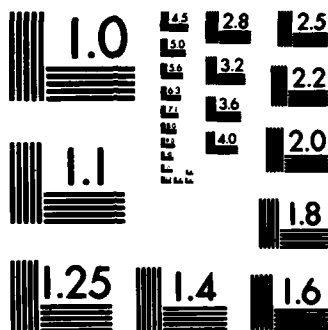

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD-A186 296

OFFICE OF NAVAL RESEARCH

Contract N00014-84-G-0201

Task No. 0051-865

Technical Report #17

DTIC FILE COPY

DTIC
ELECTE
OCT 14 1987
S D

Electrocatalytic Reduction of Molecular Oxygen by Mononuclear
and Binuclear Cobalt Phthalocyanines

By

Michael R. Hempstead, A.B.P. Lever, and Clifford C. Leznoff

in

Canadian Journal of Chemistry

York University
Department of Chemistry
4700 Keele St., North York
Ontario, Canada M3J 1P3

Reproduction in whole, or in part, is permitted for any purpose of the United States Government

*This document has been approved for public release and sale; its distribution is unlimited

*This statement should also appear in Item 10 of the Document Control Data-DD form 1473. Copies of the form available from cognizant contract administrator

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION			1b. RESTRICTIVE MARKINGS		
2a. SECURITY CLASSIFICATION AUTHORITY Unclassified			3. DISTRIBUTION/AVAILABILITY OF REPORT As it appears on the report		
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE					
4. PERFORMING ORGANIZATION REPORT NUMBER(S) Report # 17			5. MONITORING ORGANIZATION REPORT NUMBER(S)		
6a. NAME OF PERFORMING ORGANIZATION A.B.P. Lever, York University Chemistry Department		6b. OFFICE SYMBOL (If applicable)		7a. NAME OF MONITORING ORGANIZATION Office of Naval Research	
6c. ADDRESS (City, State, and ZIP Code) 4700 Keele St., North York, Ontario M3J 1P3 Canada		7b. ADDRESS (City, State, and ZIP Code) Chemistry Division 800 N. Quincy Street Arlington, VA 22217 U.S.A.			
8a. NAME OF FUNDING/SPONSORING ORGANIZATION		8b. OFFICE SYMBOL (If applicable)		9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N00014-84-G-0201	
8c. ADDRESS (City, State, and ZIP Code)		10. SOURCE OF FUNDING NUMBERS			
		PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification) Electrocatalytic Reduction of Molecular Oxygen by Mononuclear and Binuclear Cobalt Phthalocyanines					
12. PERSONAL AUTHOR(S) Hempstead, Michael R.; Lever, Alfred B.P.; and Leznoff, Clifford C.					
13a. TYPE OF REPORT Technical		13b. TIME COVERED FROM Aug/86 TO Aug/87		14. DATE OF REPORT (Year, Month, Day) August 1987	
15. PAGE COUNT 41					
16. SUPPLEMENTARY NOTATION					
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number) phthalocyanine, electronic spectra, monolayers cofacial phthalocyanine, electrochemistry, electrocatalysis, oxygen reduction.		
FIELD	GROUP	SUB-GROUP			
19. ABSTRACT (Continue on reverse if necessary and identify by block number) Investigations of the electrocatalytic activity of mononuclear and binuclear cobalt phthalocyanines for the reduction of molecular oxygen established that the latter compounds are more effective catalysts than the corresponding mononuclear species. A correlation between the half-bandwidths for the Q band of these species and their catalytic efficiency, expressed as a kinetically-limited current, suggests that the increase in activity may be attributed to electronic coupling between the phthalocyanine rings. <i>Key</i>					
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT ☒ UNCLASSIFIED/UNLIMITED ☐ SAME AS RPT ☐ DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION Unclassified/unlimited		
22a. NAME OF RESPONSIBLE INDIVIDUAL Dr. Robert K. Grasselli			22b. TELEPHONE (Include Area Code)		22c. OFFICE SYMBOL

DL/1113/87/2

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code L52 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 610P Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1



Accession For	
NTIS CRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By	
Distribution /	
Availability /	
DTIC	
A-1	

ABSTRACTS DISTRIBUTION LIST, 359/627

- | | |
|---|---|
| Dr. Manfred Breiter
Institut für Technische Elektrochemie
Technischen Universität Wien
9 Getreidemarkt, 1160 Wien
AUSTRIA | Dr. Roger Belt
Litton Industries Inc.
Airtron Division
Morris Plains, NJ 07950 |
| Dr. E. Yeager
Department of Chemistry
Case Western Reserve University
Cleveland, Ohio 44106 | Dr. Ulrich Stimming
Department of Chemical Engineering
Columbia University
New York, NY 10027 |
| Dr. R. Sutula
The Electrochemistry Branch
Naval Surface Weapons Center
Silver Spring, Maryland 20910 | Dr. Royce W. Murray
Department of Chemistry
University of North Carolina
Chapel Hill, North Carolina 27514 |
| Dr. R. A. Marcus
Department of Chemistry
California Institute of Technology
Pasadena, California 91125 | Dr. Michael J. Weaver
Department of Chemistry
Purdue University
West Lafayette, Indiana 47907 |
| Dr. J. J. Auborn
AT&T Bell Laboratories
600 Mountain Avenue
Murray Hill, New Jersey 07974 | Dr. R. David Rauh
EIC Laboratories, Inc.
Norwood, Massachusetts 02062 |
| Dr. M. S. Wrighton
Chemistry Department
Massachusetts Institute
of Technology
Cambridge, Massachusetts 02139 | Dr. Edward M. Eyring
Department of Chemistry
University of Utah
Salt Lake City, UT 84112 |
| Dr. B. Stanley Pons
Department of Chemistry
University of Utah
Salt Lake City, Utah 84112 | Dr. M. M. Nicholson
Electronics Research Center
Rockwell International
3370 Miraloma Avenue
Anaheim, California |
| Dr. Bernard Spielvogel
U.S. Army Research Office
P.O. Box 12211
Research Triangle Park, NC 27709 | Dr. Nathan Lewis
Department of Chemistry
Stanford University
Stanford, California 94305 |
| Dr. Mel Miles
Code 3852
Naval Weapons Center
China Lake, California 93555 | Dr. Hector D. Abruna
Department of Chemistry
Cornell University
Ithaca, New York 14853 |
| Dr. P. P. Schmidt
Department of Chemistry
Oakland University
Rochester, Michigan 48063 | Dr. A. B. P. Lever
Chemistry Department
York University
Downsview , Ontario M3J 1P3 |

ABSTRACTS DISTRIBUTION LIST, 359/627

Dr. Martin Fleischmann
Department of Chemistry
University of Southampton
Southampton SO9 5H UNITED KINGDOM

Dr. John Wilkes
Department of the Air Force
United States Air Force Academy
Colorado Springs, Colorado 80840-6528

Dr. R. A. Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. Janet Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. A. J. Bard
Department of Chemistry
University of Texas
Austin, Texas 78712

Dr. Steven Greenbaum
Department of Physics and Astronomy
Hunter College
695 Park Avenue
New York, New York 10021

Dr. Donald Sandstrom
Boeing Aerospace Co.
P.O. Box 3999
Seattle, Washington 98124

Mr. James R. Moden
Naval Underwater Systems Center
Code 3632
Newport, Rhode Island 02840

Dr. D. Rolison
Naval Research Laboratory
Code 6171
Washington, D.C. 20375-5000

Dr. D. F. Shriver
Department of Chemistry
Northwestern University
Evanston, Illinois 60201

Dr. Alan Bewick
Department of Chemistry
The University of Southampton
Southampton, SO9 5NH UNITED KINGDOM

Dr. Edward Fletcher
Department of Mechanical Engineering
University of Minnesota
Minneapolis, Minnesota 55455

Dr. Bruce Dunn
Department of Engineering &
Applied Science
University of California
Los Angeles, California 90024

Dr. Elton Cairns
Energy & Environment Division
Lawrence Berkeley Laboratory
University of California
Berkeley, California 94720

Dr. Richard Pollard
Department of Chemical Engineering
University of Houston
Houston, Texas 77004

Dr. M. Philpott
IBM Research Division
Mail Stop K 33/801
San Jose, California 95130-6099

Dr. Martha Greenblatt
Department of Chemistry, P.O. Box 939
Rutgers University
Piscataway, New Jersey 08855-0939

Dr. Anthony Sammells
Eltron Research Inc.
4260 Westbrook Drive, Suite 111
Aurora, Illinois 60505

Dr. C. A. Angell
Department of Chemistry
Purdue University
West Lafayette, Indiana 47907

Dr. Thomas Davis
Polymers Division
National Bureau of Standards
Gaithersburg, Maryland 20899

ABSTRACTS DISTRIBUTION LIST, 359/627

Dr. Stanislaw Szpak
Naval Ocean Systems Center
Code 633, Bayside
San Diego, California 95152

Dr. Gregory Farrington
Department of Materials Science
and Engineering
University of Pennsylvania
Philadelphia, Pennsylvania 19104

Dr. John Fontanella
Department of Physics
U.S. Naval Academy
Annapolis, Maryland 21402-5062

Dr. Micha Tomkiewicz
Department of Physics
Brooklyn College
Brooklyn, New York 11210

Dr. Lesser Blum
Department of Physics
University of Puerto Rico
Rio Piedras, Puerto Rico 00931

Dr. Joseph Gordon, II
IBM Corporation
5600 Cottle Road
San Jose, California 95193

Dr. Joel Harris
Department of Chemistry
University of Utah
Salt Lake City, Utah 84112

Dr. J. O. Thomas
University of Uppsala
Institute of Chemistry
Box 531 Baltimore, Maryland 21218
S-751 21 Uppsala, Sweden

Dr. John Owen
Department of Chemistry and
Applied Chemistry
University of Salford
Salford M5 4WT UNITED KINGDOM

Dr. O. Stafstudd
Department of Electrical Engineering
University of California
Los Angeles, California 90024

Dr. Boone Owens
Department of Chemical Engineering
and Materials Science
University of Minnesota
Minneapolis, Minnesota 55455

Dr. Johann A. Joebstl
USA Mobility Equipment R&D Command
DRDME-EC
Fort Belvoir, Virginia 22060

Dr. Albert R. Landgrebe
U.S. Department of Energy
M.S. 68025 Forrestal Building
Washington, D.C. 20595

Dr. J. J. Brophy
Department of Physics
University of Utah
Salt Lake City, Utah 84112

Dr. Charles Martin
Department of Chemistry
Texas A&M University
College Station, Texas 77843

Dr. Milos Novotny
Department of Chemistry
Indiana University
Bloomington, Indiana 47405

Dr. Mark A. McHugh
Department of Chemical Engineering
The Johns Hopkins University
Baltimore, Maryland 21218

Dr. D. E. Irish
Department of Chemistry
University of Waterloo
Waterloo, Ontario, Canada
N2L 3G1

ABSTRACTS DISTRIBUTION LIST, 359/627

Dr. Henry S. White
Department of Chemical Engineering
and Materials Science
151 Amundson Hall
421 Washington Avenue, S.E.
Minneapolis, Minnesota 55455

Dr. Daniel A. Buttry
Department of Chemistry
University of Wyoming
Laramie, Wyoming 82071

Dr. W. R. Fawcett
Department of Chemistry
University of California
Davis, California 95616

Dr. Peter M. Blonsky
Eveready Battery Company, Inc.
25225 Detroit Road, P.O. Box 45035
Westlake, Ohio 44145

ABSTRACTS DISTRIBUTION LIST, 051A

Dr. M. A. El-Sayed
Department of Chemistry
University of California
Los Angeles, California 90024

Dr. E. R. Bernstein
Department of Chemistry
Colorado State University
Fort Collins, Colorado 80521

Dr. J. R. MacDonald
Chemistry Division
Naval Research Laboratory
Code 6110
Washington, D.C. 20375-5000

Dr. G. B. Schuster
Chemistry Department
University of Illinois
Urbana, Illinois 61801

Dr. J. B. Halpern
Department of Chemistry
Howard University
Washington, D.C. 20059

Dr. M. S. Wrighton
Department of Chemistry
Massachusetts Institute of Technology
Cambridge, Massachusetts 02139

Dr. W. E. Moerner
I.B.M. Corporation
Almaden Research Center
650 Harry Rd.
San Jose, California 95120-6099

Dr. A. B. P. Lever
Department of Chemistry
York University
Downsview, Ontario
CANADA M3J1P3

Dr. George E. Walrafen
Department of Chemistry
Howard University
Washington, D.C. 20059

Jr. Joe Brandelik
AFWAL/AADO-1
Wright Patterson AFB
Fairborn, Ohio 45433

Dr. Carmen Ortiz
Consejo Superior de
Investigaciones Cientificas
Serrano 121
Madrid 6, SPAIN

Dr. Kent R. Wilson
Chemistry Department
University of California
La Jolla, California 92093

Dr. G. A. Crosby
Chemistry Department
Washington State University
Pullman, Washington 99164

Dr. Theodore Pavlopoulos
NOSC
Code 521
San Diego, California 91232

Dr. John Cooper
Code 6173
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. Joseph H. Boyer
Department of Chemistry
University of New Orleans
New Orleans, Louisiana 70148

Dr. Harry D. Gafney
Department of Chemistry
Queens College of CUNY
Flushing, New York 11367-0904

CANADIAN JOURNAL
OF CHEMISTRY

Electrocatalytic Reduction of Molecular Oxygen by Mononuclear
and Binuclear Cobalt Phthalocyanines

Michael R. Hempstead*, A.B.P. Lever* and Clifford C. Leznoff,
York University, North York, Ontario, Canada, M3J 1P3.

A.B.P. Lever (416) 736-5246

Abstract

Investigations of the electrocatalytic activity of mononuclear and binuclear cobalt phthalocyanines for the reduction of molecular oxygen established that the latter compounds are more effective catalysts than the corresponding mononuclear species. A correlation between the half-bandwidths for the 0 band of these species and their catalytic efficiency, expressed as a kinetically-limited current, suggests that the increase in activity may be attributed to electronic coupling between the phthalocyanine rings.

Introduction

If a fuel cell is to operate efficiently, a catalyst must be embedded in the cathode to accelerate the reduction of oxygen gas. This catalyst must be capable of withstanding the operating conditions of the fuel cell (strong acid or base, fairly high temperatures), for long periods of time, without loss of activity. Platinum is commonly used as a fuel cell catalyst, but is expensive representing some 10% of the total fuel cell cost. Catalysts which are more effective, and less expensive are needed, if fuel cell applications are to become viable.

Many mononuclear metal porphyrins act as electrocatalysts (1-21) but the work of Collman and Anson (22-28) and Chang (29-35) has revealed that certain binuclear porphyrins are much more effective. Similarly, mononuclear phthalocyanines of iron and cobalt are effective (36-50), but some ill-characterised 'dimeric' and polymeric phthalocyanines appear more effective (51-62). Savy (54-56) performed ESCA, ESR, Mössbauer and optical spectroscopic studies to establish correlations between the spectroscopic properties of polymeric and monomeric iron phthalocyanines and the electrocatalytic activity of these species towards oxygen reduction. We consider here a correlation between the optical spectra of a series of well-characterized mono- and binuclear cobalt phthalocyanines and

their electrocatalytic activity.

The binuclear porphyrins studied by Collman and Anson are too fragile for long-term use under fuel cell conditions and therefore our studies have been directed towards thermally more stable binuclear phthalocyanine compounds. We have recently reported (63-65) a series of binuclear phthalocyanine complexes of the general formula $[M\text{-tri(neopentoxy)phthalocyanine}]_2(\text{bridge})$ where the bridge may contain 1,2,4 or 5 atoms, and where M may be H_2 , Cu or Co. The three neopentoxy groups are randomly distributed in the 4 or 5 positions of the three unbridged benzene rings, providing solubility in many organic solvents e.g. toluene, o-dichlorobenzene and dichloroethane, but generally not acetone and ethanol.

Of relevance to this presentation are the following species, with their abbreviations (the number in parentheses is the number of bridging atoms connecting the two phthalocyanine rings):

CoTNPc 2,9,16,23-tetraneopentoxypthalocyanatocobalt(II).

This is the mononuclear control molecule.

O(1)[CoTrNPc]₂ bis-2-(9,16,23-trineopentoxypthalocyaninyl)cobalt(II))ether; two phthalocyanine rings linked by a single oxygen (ether) bridge.

C(2)[CoTrNPc]₂ 1,2-bis-2'-(9',16',23'-trineopentoxypthalocyaninyl)cobalt(II))ethane; two phthalocyanine rings linked by a single carbon (ethane) bridge.

cyaninylcobalt(II))ethane; two phthalocyanine rings linked by an ethane $-\text{CH}_2\text{CH}_2-$ bridge.

Cat(4)[CoTrNPc]₂ 1,2-bis-2'-(9',16',23'-trineopentoxypthalocyaninoxycobalt(II))benzene; two phthalocyanine rings linked by a catechol $-\text{O}-\text{C}_6\text{H}_4-\text{O}-$ bridge.

EtMeO(5)[CoTrNPc]₂ 1,3-bis-2'-(9',16',23'-trineopentoxypthalocyaninoxycobalt(II))-2-ethyl-2-methylpropane; two phthalocyanine rings attached linked by a $-\text{OCH}_2\text{C}(\text{Et})(\text{Me})\text{CH}_2\text{O}-$ bridge.

Earlier investigations of the metal-free analogues of these species (66) established properties of these compounds which are relevant to the observations reported here. These properties are:

- i) In condensed phases (frozen solution glass, Nujol mull, etc.), these complexes may exhibit intermolecular aggregation. In dilute solution, $<5 \times 10^{-5}$ M, intermolecular aggregation is generally absent (67).
- ii) Some binuclear phthalocyanines may close upon themselves ('clamshell' behaviour) to aggregate via cofacial intramolecular aggregation. Specifically, of the metal-free species, only Cat(4)[TrNPcH₂]₂ and EtMeO(5)[TrNPcH₂]₂ are capable of such intramolecular aggregation. Such species exist in a dynamic equilibrium with 'open' conformations.
- iii) The electronic spectra of the metal-free species show evidence of the coupling of the transition moments on each

phthalocyanine ring (66). Thus direct through space coupling is observed in the cofacial conformations, giving rise to a blue shift in the Q and Soret absorptions. However, a blue shift is also observed in the other metal-free species, as a consequence of coupling through space (or through the bridge) in 'open', non-aggregated conformations.

Note that electronic coupling is more readily detected in the electronic spectra of binuclear phthalocyanine species, relative to comparable porphyrin species, because the visible region transition moments are much larger in the former case (68).

Experimental

The species Co(II)TNPC (64), $\text{EtMeO(5)[Co(II)TrNPc]}_2$ (64), $\text{C(2)[Co(II)TrNPc]}_2$ (65), $\text{Cat(4)[Co(II)TrNPc]}_2$ (65) and $\text{O(1)[Co(II)TrNPc]}_2$ (69) were prepared by literature routes. Aldrich Gold Label o-dichlorobenzene (DCB) was used without further purification and Fisher certified 1 N sodium hydroxide was diluted as required for the aqueous studies. Water was purified by double-distillation over KMnO_4 followed by passage through a Barnstead organic removal cartridge and two Barnstead mixed resin ultrapure cartridges. Stress-annealed pyrolytic graphite (SAPG) and ordinary pyrolytic graphite (OPG), obtained from Union Carbide, were used as electrode materials. The

graphite was mounted in Teflon to expose a circular area of 0.490 cm^2 for the SAPG electrode and 0.493 cm^2 for the OPG electrode. Before each experiment, the electrode surface was cleaned by successive polishings with $1.0 \text{ }\mu\text{m}$, $0.3 \text{ }\mu\text{m}$ and $0.05 \text{ }\mu\text{m}$ alumina (Linde) suspended in water on Metron polishing cloth. Argon gas (Linde) was purified by passage through heated copper filings, anhydrous CaSO_4 (Drierite), molecular sieves (BDH Type 3A), and glass wool. Oxygen gas (Linde) was purified by passage through anhydrous CaSO_4 , NaOH pellets (AnalaR analytical grade), anhydrous CaSO_4 , molecular sieves and glass wool. Tetrabutylammonium perchlorate (TBAP) (Eastman Kodak) was recrystallized from absolute ethanol and dried in a vacuum oven at 50°C for two days. Potential scans were performed with a Pine Instruments RD3 potentiostat and the rotation studies with a Pine Instruments PIR rotator. The cell for the adsorption experiments employed a medium frit to separate a silver wire quasi-reference electrode from the main chamber containing the OPG working electrode and a platinum wire counter electrode. The cell for the aqueous studies comprised a separate chamber for each electrode with a Luggin capillary extending from the reference chamber to the proximity of the OPG surface. For all aqueous experiments, the potential was measured versus a saturated calomel electrode (SCE).

Phthalocyanine solutions were prepared in DCB with

0.1 M TBAP as supporting electrolyte, such that the concentration was ca. 10 μ M with respect to the TNPC unit. These solutions were purged with argon for about an hour before scanning the working electrode at a rate of 100 mV/s over the range 0.00 to +1.00 V versus the silver wire. Adsorbed layers on OP6 or SAP6 electrodes were obtained by cycling until the anodic and cathodic peak currents associated with the adsorbed species remained constant over five minutes of continuous scanning. When this condition was satisfied, the adsorbed layer was assumed to have reached a steady coverage. Scans at various rates were then recorded to determine the surface coverage (vide infra).

The catalytic efficiency of the various phthalocyanine compounds was investigated with the adsorbed species on the OP6 electrode. This modified electrode was removed from the phthalocyanine solution, washed with ethanol, then with water, and finally placed in the cell for the aqueous studies. The 0.10 M NaOH solution in this cell had been purged with oxygen for several hours to ensure saturation. The electrode was then scanned over the range 0.00 to -1.00 V versus SCE at a rate of 10 mV/s for rotation rates ranging from 400 to 10,000 rpm. After each scan, the electrode was held at 0.00 V for 1 minute to permit the rotation rate to be changed for the next scan.

Results

I) Adsorption Studies

Some preliminary adsorption experiments were performed on a SAPG electrode to determine the electronic nature and orientation of the adsorbed species. The cyclic voltammograms for a solution of 2.5×10^{-5} M CoTNPC in DCB and 0.1 M TBAP studied at a SAPG working electrode, as shown in Figure 1, display two couples in close proximity. Following deconvolution of these waves (70), a plot (Figure 2A) of cathodic peak current, $i_{p,c}$, versus scan rate, v , for couple I ($R = 0.999$) and a plot (Figure 2B) of $i_{p,c}$ versus $\sqrt{v}$ for couple II ($R = 0.998$) indicated that these couples were adsorption and diffusion processes (71), respectively. From the relative positions of couples I and II, it follows that the adsorbed species binds most strongly in the reduced form associated with couple II (72), although the presence of a reductive adsorption wave indicates that the oxidized form associated with this couple also binds to the electrode. Couple II is associated with the ligand process $[\text{Co(II)TNPC}(-1)]^+/\text{Co(II)TNPC}(-2)$ (73) and therefore CoTNPC binds to the graphite surface most strongly as $\text{Co(II)TNPC}(-2)$. The binding between the CoTNPC and the SAPG electrode can be explained by π - π interactions between the phthalocyanine ring and the graphite lattice, if the CoTNPC is adsorbed flat to the

SAPG surface. This mode of adsorption has also been suggested in a similar investigation (41) by Yeager and coworkers who studied cobalt tetrasulphonate phthalocyanine (CoTSPc).

In addition to the electronic nature and orientation of the adsorbed molecule, the extent of coverage of the catalyst on the electrode surface must be known. Quantitative analysis requires the selection of an appropriate adsorption isotherm to describe the cyclic voltammetric response of the adsorbate. An adsorption isotherm describes the relationship between the concentrations of the adsorbate in the adsorption layer and in the bulk phase from which the adsorption takes place. Appropriate isotherms may also yield information about interactions between molecules in the adsorption layer.

The Langmuir isotherm was used to analyse the adsorption of CoTNpc on a SAPG electrode. This isotherm applies to systems in which there are no interactions between the adsorbed molecules (72). For systems which satisfy these conditions, the value of n may be calculated from the peak-width-at-half-height, $W_{1/2}$, from the expression

$$[1] \quad n = \frac{2RT}{W_{1/2}F} \ln(3+2\sqrt{2})$$

The average value of n calculated in this fashion was 1.00 ± 0.02 in excellent agreement with our expectation of a one-electron

process. By calculating the charge under the adsorption peak and assuming the area of a phthalocyanine molecule, A_{PC} , is $200 \text{ \AA}^2$ (41), the coverage of CoTNPC on a SAPG electrode was determined to be about 0.3 ± 0.1 monolayers. This low level of coverage is consistent with another study (41) in which CoTSPc adsorbed on SAPG to the extent of 0.4 monolayers.

Since a coverage of between one and two monolayers was desired for these oxygen reduction studies, SAPG was not used for these investigations. (Recent studies have established a method for obtaining a coverage of one monolayer on SAPG which will be employed in later investigations.) Yeager and coworkers (42) found that CoTSPc could be adsorbed on OPG to about four times the coverage on SAPG; the greater adsorption on the OPG electrode was attributed to a higher density of surface defects assumed to be critical to adsorption (74). Adsorption experiments with CoTNPC and an OPG electrode did show enhanced adsorption, as shown in Figure 3. This increased adsorption affects the cyclic voltammograms in many ways. The most readily apparent effect is the loss of the diffusion wave which had been observed in conjunction with an adsorption wave when using SAPG. Since the adsorption wave overwhelms the diffusion wave under the conditions employed for this experiment (71), later calculations of surface coverage disregard contributions from diffusion and treat this as a pure

adsorption process. The other noticeable effect in Figure 3 is the large peak separation observed at higher scan rates. This probably arises from the larger currents observed in this scan and the high iR drop in these DCB solutions.

The adsorption studies with the OPG electrode were analysed with the Langmuir isotherm which gave an average n value of 0.72 ± 0.04 , suggesting that the use of the Langmuir isotherm was not appropriate for this system. An alternate choice, the Frumkin isotherm (75-78), is useful for systems in which there are interactions between adsorbed molecules. A recent investigation (78) of several isotherms suggests that the Frumkin isotherm is most appropriate for electrochemical processes involving the adsorption of organic compounds. According to the Frumkin isotherm, the peak current and the value of n are given by the expressions (77)

$$[2] \quad i_p = \frac{n^2 F^2 A \Gamma v}{RT(4 - 2r\Gamma)}$$

$$[3] \quad n = \frac{2RT}{W_{1/2}F} \left[\ln P - r\Gamma \frac{P-1}{P+1} \right]$$

where r is an interaction parameter (cm^2/mol), Γ is the surface concentration of the adsorbed species (mol/cm^2), and P is given by

$$[4] \quad P = 3 - r\Gamma + (r^2\Gamma^2 - 6r\Gamma + 8)^{1/2}$$

Repulsive interactions are denoted by negative values of r

while stabilizing interactions are denoted by positive values of r . If the interactions between adsorbed molecules are repulsive, the wave broadens and the peak decreases, but if the interactions are attractive, the wave narrows and the peak increases. If the interaction parameter is zero, then the Frumkin isotherm expressions simplify to those given by the Langmuir isotherm.

The cyclic voltammograms from the adsorption studies on OPG displayed waves which were broader and more rounded than those observed for the SAPG experiments. This change in waveshape indicates that at these higher coverages, repulsive interactions exist between molecules adsorbed on the electrode surface. The voltammograms which had been analysed by the Langmuir isotherm to give an average n value of 0.72 ± 0.04 when analysed by the Frumkin isotherm yielded 0.93 ± 0.03 in much better agreement with the expected value of unity.

Average values of the dimensionless parameters $r\Gamma$ and the average surface coverage, θ , (where $\theta = \Gamma/\Gamma_{\text{Pc}}$) are presented in Table 1 for an OPG electrode modified with CoTNPC or one of its binuclear derivatives. The surface coverage calculations for the binuclear compounds used the same area approximation per phthalocyanine unit as had been used for CoTNPC since these calculations were designed to estimate the number of cobalt atoms on the electrode surface, not the number of

phthalocyanine molecules. As a means of clarifying this point, consider the following example. If a value of 2.0 is calculated for θ , this could indicate that the electrode is covered by two monolayers of the mononuclear species, two layers of a binuclear species in an 'open' configuration, or one layer of a binuclear species in a cofacial configuration. Consideration of steric restraints in these molecules and the behaviour of these species in solution is required to infer the manner in which these molecules adsorb on the electrode surface.

The θ value of 1.4 ± 0.4 for CoTNPC-modified OPG electrodes is most likely indicative of a coverage of one monolayer. The reported θ may be somewhat high as it is based on the geometric area of the electrode and does not account for the inherent roughness of the surface. It is improbable that a second layer forms on the surface since none of the adsorbate is lost after washing and transferring to an aqueous solution. A weakly bound second layer of CoTSPc on OPG has been reported (74), but it was readily removed by washing.

The average coverage for the molecule $O(1)[CoTrNPc]_2$ was 1.3 ± 0.4 , which is quite similar to that found for CoTNPC. The adsorption of $O(1)[CoTrNPc]_2$ was anticipated to be similar to that of CoTNPC because this binuclear species can only exist in

an 'open' conformation. The $O(1)[CoTrNPc]_2$ molecule would adsorb with one ring flat on the OPG surface while the other ring lies at some oblique orientation. The ring in the oblique orientation would give this surface a highly disordered structure and, from the r_f value in Table 1, it would appear that it also leads to abnormally high repulsive interactions.

The remaining binuclear phthalocyanines have average θ values near two. If these molecules adsorbed on to the electrode surface in an 'open' conformation then a θ value near two would not be expected since, as noted earlier, the π - π interactions which arise between the first and second layer of phthalocyanine molecules adsorbed on the electrode surface are too weak to stabilize a second layer. It would therefore appear that most of these binuclear species adsorb on to the electrode surface in some sort of cofacial arrangement. This configuration is easily obtained by $Cat(4)[CoTrNPc]_2$ and $EtMeO(5)[CoTrNPc]_2$, but the stacking of $C(2)[CoTrNPc]_2$ would necessitate that the phthalocyanine rings in the second layer lie above a surface bound ring of an adjacent $C(2)[CoTrNPc]_2$ molecule. The values of r_f reported for these binuclear compounds are fairly consistent and are quite similar to the value of -0.7 reported by Collman and Anson (28) for one of their cofacial cobalt porphyrins. It has been suggested that the source of repulsions observed for flatly adsorbed aromatic


molecules such as these, is the parallel orientation of their dipoles (79).

Another interesting feature of these adsorption studies is illustrated in Figure 4. The cyclic voltammograms for $O(1)[CoTrNPc]_2$ and $Cat(4)[CoTrNPc]_2$ display one adsorption wave for the $[Co(II)TrNPc(-1)]^+/Co(II)TrNPc(-2)$ couple, just like that observed for the adsorption of $CoTrNPc$ on OPG (see Figure 3). However, the cyclic voltammograms for $C(2)[CoTrNPc]_2$ and $EtMeO(5)[CoTrNPc]_2$ display two couples in the same potential region. Plots of i_p versus v for the two couples are linear, thus both couples arise from adsorption processes. Frumkin isotherm analysis yielded values of n close to unity which, when combined with the potential of these couples, suggests that these couples are both associated with the $[Co(II)TrNPc(-1)]^+/Co(II)TrNPc(-2)$ process. The origin of these two adsorption processes may be explained in terms of the electronic coupling inherent in these binuclear compounds.

The theory of intramolecular coupling in these binuclear phthalocyanines has been presented elsewhere (66). In solution, these binuclear species are expected to exist in a dynamic equilibrium between various conformations, dependent upon the nature of the bridge since, in some cases, steric effects may provide barriers to free rotation. Therefore, the

electronic absorption spectrum of a solution of one of these binuclear species would represent the summation of the spectra of a mixture of these conformers. The coupling in these species resulted in a blue-shifted Q band which was also broadened, the degree of this broadening being a qualitative measure of the degree of electronic coupling in these binuclear species.

The half-bandwidths of the five phthalocyanine species investigated in this study are presented in Table 2 (80). The relative extent of coupling in these compounds, as established by these half-bandwidths, is as follows:



Cyclic voltammograms of each of the binuclear species are presented in Figure 4. In the voltammograms of $C(2)[CoTrNPc]_2$ and $EtMeO(5)[CoTrNPc]_2$, two adsorption waves are observed which arise from two distinct redox couples in close proximity. Similar voltammograms have been reported previously (28,81) but, in these earlier reports, both of the redox processes could be observed when the species was in solution, not bound to the electrode surface. For each of the adsorbed binuclear species, one phthalocyanine ring lies on the electrode surface while the other ring is not in contact with it. The two redox couples, therefore, are regarded to arise from the bound Pc

ring, and the bridged Pc ring which is not bound directly to the electrode. In solution, only one redox process is observed, common to both rings. In the more highly coupled species, namely O(1)[CoTrNPc]₂ and Cat(4)[CoTrNPc]₂, electron transfer across the bridge to the outer phthalocyanine ring is facile and therefore only one redox couple is observed. However, electron transfer across the saturated C(2)[CoTrNPc]₂ and EtMeO(5)[CoTrNPc]₂ bridges is inhibited and therefore the redox potential for the outer phthalocyanine ring could differ from that of the inner phthalocyanine ring. Although the O(1)[CoTrNPc]₂ bridge is, technically, also a saturated bridge, it is apparent from the half-bandwidth studies mentioned above, that electron transfer across this bridge is permissible. This proposal could explain the differences between the cyclic voltammograms given in Figure 4, although further study would be necessary to establish the source of this behaviour conclusively.

II)Oxygen Studies

The catalytic properties of these phthalocyanine species were investigated by means of rotating disc electrode (RDE) studies. The diffusion-limited current for such an experiment, expressed in mA, is described by the expression (82)

$$[6] \quad i_L = 1000nAFc \left(\frac{2\pi U \omega}{60} \right)^{1/2} \left[\frac{0.62048S^{-2/3}}{1 + 0.2980S^{-1/3} + 0.14514S^{-2/3}} \right]$$

where U is the kinematic viscosity (cm^2/s), ω is the rotation rate (rpm), S is the Schmidt number ($S = U/D$), A is the electrode area (cm^2), F is Faraday's constant, and C is the concentration of O_2 (mol/cm^3). A Levich plot (i_L versus $\omega^{1/2}$) of the diffusion-limited O_2 reduction current at a CoTNPC-modified OPG electrode is shown in Figure 5. In the calculation of i_L for this Levich plot, the diffusion coefficient and concentration of O_2 were taken as $1.67 \times 10^{-5} \text{ cm}^2/\text{s}$ (42) and $1.38 \times 10^{-6} \text{ mol}/\text{cm}^3$ (83), respectively, the kinematic viscosity was estimated at $9.97 \times 10^{-3} \text{ cm}^2/\text{s}$ (84), the Schmidt number was calculated to be 597, and the value used for n was two. The good agreement between the calculated diffusion-limited current and the experimentally observed limiting current suggests that O_2 is undergoing a two-electron reduction to peroxide rather than a four-electron reduction to water. Further evidence for this two-electron reductive pathway will be presented later.

If an electrode process is hindered by a kinetic step, a plot of i_L , or i , versus $\omega^{1/2}$ deviates from the linear relationship given in equation 6 (71). The effect of this kinetic step on the current that flows in the potential region of mixed diffusion-kinetic control for a first-order process under steady-state conditions is given by the expression


(86-88):

$$[7] \quad 1/i = 1/i_k + 1/i_L$$

in which i_k is the kinetically-limited current. A plot of $1/i$ versus $1/\omega^{1/2}$, known as the Koutecky-Levich plot, establishes this kinetically-limited current which is equivalent to the current that would flow if the concentration of O_2 at the electrode surface could be maintained at its bulk concentration during the reduction process. Therefore, i_k at a given potential is directly proportional to the maximum rate at which O_2 can be reduced to peroxide at the catalyst-modified electrode at that potential (89).

The reduction of O_2 at an OPG electrode modified with CoTNPC is shown in Figure 6. These scans were recorded at 10 mV/s, but may be considered to be steady-state curves since no hysteresis was observed between the forward and reverse scans. Following the procedures presented by Frumkin and Tedoradse (90), Koutecky-Levich plots at -0.450 V, -0.500 V, -0.550 V and -0.600 V were constructed. Koutecky-Levich plots of O_2 reduction at -0.450 V for OPG electrodes modified with CoTNPC and each of its binuclear derivatives are given in Figure 7. The scatter for Koutecky-Levich plots was small ($R > .999$) and the n values calculated from the slopes of these plots (Table 3) were consistent with a two-electron process yielding peroxide as the reduction product. The different

intercepts for the Koutecky-Levich plots illustrate that the catalytic activity of these species differ. The kinetically-limited currents for oxygen reduction are presented in Table 4. These kinetically-limited currents have been normalized to the CoTNPC data to rank the catalytic efficiency of the binuclear species and these normalized kinetically-limited currents are presented as the bracketed values in Table 4. The standard deviation for the average normalized kinetically-limited currents is less than 15% which though somewhat large, is similar to the deviation reported in another study (91). These normalized currents indicate the reactivities of these species towards oxygen reduction are as follows:



It is surely significant that this ranking is the same as given for the electronic coupling of these species.

Although the binuclear CoTNPC compounds have shown increased activity towards the electrocatalytic reduction of molecular oxygen, the potential at which this process occurs in pH 13 NaOH solution is approximately the same as that for CoTSPc under the same conditions (41), and rather too negative to be practical for a fuel cell catalyst. Present studies are being directed towards the shifting of the molecular oxygen reduction potential to more positive values by performing

these experiments under acidic conditions, and also to devise conditions under which the direct four-electron reduction process will be favoured.

Summary

In basic media, binuclear cobalt phthalocyanines were shown to be more active towards the electrocatalytic reduction of molecular oxygen than the corresponding mononuclear species. The increased activity of these binuclear compounds has been attributed to the increased electronic coupling between the phthalocyanine rings of these species. Current studies include CoPc species showing a much greater degree of intramolecular coupling than observed here (92). A mechanistic study of CoTNPc over the pH range 1 to 13 will also be reported shortly.

Acknowledgements

Gratitude is extended to the Natural Sciences and Engineering Research Council of Canada for financial support in the forms of an operating grant and a postgraduate scholarship [MRH]. Support from the Office of Naval Research (Washington) is also appreciated. The authors also wish to express their gratitude to Dr. Pavel Janda for beneficial discussions.

References

- (1) T. Kuwana, M. Fujihira, K. Sunakawa and T. Osa, J. Electroanal. Chem., **88**, 299 (1978).
- (2) A. Bettelheim and T. Kuwana, Anal. Chem., **51**, 2257 (1979).
- (3) A. Bettelheim, R.J.H. Chan and T. Kuwana, J. Electroanal. Chem., **99**, 391 (1979).
- (4) N. Kobayashi, T. Matsue, M. Fujihira and T. Osa, J. Electroanal. Chem., **103**, 427 (1979).
- (5) M.R. Tarasevich and K.A. Radyushkina, Russ. Chem. Rev. Engl. Transl., **49**, 1498 (1980).
- (6) J.A.R. van Veen, J.F. van Baar, C.J. Kroese, J.G.F. Coolegem, N. de Wit and H.A. Colijn, Ber. Bunsenges. Phys. Chem., **85**, 693 (1981).
- (7) J.A.R. van Veen and H.A. Colijn, Ber. Bunsenges. Phys. Chem., **85**, 700 (1981).
- (8) P.A. Forshey, T. Kuwana, N. Kobayashi and T. Osa, Adv. Chem. Ser., **201**, 601 (1982).
- (9) N. Kobayashi, M. Fujihira, T. Osa and S. Dong, Chem. Lett., **575** (1982).
- (10) A. Bettelheim, R. Parash and D. Ozer, J. Electrochem. Soc., **129**, 2247 (1982).
- (11) N. Kobayashi and T. Osa, J. Electroanal. Chem., **157**, 269 (1983).

- (12) A. Bettelheim, D. Ozer and R. Parash, J. Chem. Soc.,
Faraday Trans. 1, 79, 1555 (1983).
- (13) P.A. Forshey and T. Kuwana, Inorg. Chem., 22, 699 (1983).
- (14) K. Okabayashi, O. Ikeda and H. Tamura, J. Chem. Soc.,
Chem. Commun., 684 (1983).
- (15) O. Ikeda, K. Okabayashi and H. Tamura, Chem. Lett., 1821
(1983).
- (16) O. Ikeda, H. Fukuda and H. Tamura, J. Chem. Soc., Chem.
Commun., 567 (1984).
- (17) D. Ozer, R. Parash, F. Broitman, U. Mor and A. Bettelheim,
J. Chem. Soc., Faraday Trans. 1, 80, 1139 (1984).
- (18) O. Ikeda, H. Fukuda, T. Kojima and H. Tamura, J.
Electrochem. Soc., 132, 3069 (1985).
- (19) C.-L. Ni and F.C. Anson, Inorg. Chem., 24, 4754 (1985).
- (20) F. Bedioui, C. Bongars, C. Hinnen, C. Bied-Charreton and
J. Devynck, Bull. Chim. Soc. Fr., 679 (1985).
- (21) O. Ikeda, K. Okabayashi, N. Yoshida and H. Tamura, J.
Electroanal. Chem., 191, 157 (1985).
- (22) J.P. Collman, M. Marocco, P. Denisevich, C. Koval and F.C.
Anson, J. Electroanal. Chem., 101, 117 (1979).
- (23) J.P. Collman, P. Denisevich, Y. Konai, M. Marocco, C.
Koval and F.C. Anson, J. Am. Chem. Soc., 102, 6027 (1980).
- (24) R.R. Durand, Jr., J.P. Collman and F.C. Anson, J.
Electroanal. Chem., 151, 289 (1983).

- (25) J.P. Collman, F.C. Anson, C.E. Barnes, C.S. Bencosme, T. Geiger, E.R. Evitt, R.P. Kreh, K. Meier and R.B. Pettman, *J. Am. Chem. Soc.*, **105**, 2694 (1983).
- (26) J.P. Collman, C.S. Bencosme, R.R. Durand, Jr., R.P. Kreh and F.C. Anson, *J. Am. Chem. Soc.*, **105**, 2699 (1983).
- (27) J.P. Collman, F.C. Anson, C.E. Barnes and B.D. Miller, *J. Am. Chem. Soc.*, **105**, 2704 (1983).
- (28) R.R. Durand, Jr., C.S. Bencosme, J.P. Collman and F.C. Anson, *J. Am. Chem. Soc.*, **105**, 2710 (1983).
- (29) C.K. Chang, *J. Chem. Soc., Chem. Commun.*, 800 (1979).
- (30) C.K. Chang, *Biochem. Clin. Aspects Oxygen*, 437 (1978).
- (31) C.K. Chang, *Adv. Chem. Ser.*, **173**, 162 (1979).
- (32) H.Y. Liu, M.J. Weaver, C.-B. Wang and C.K. Chang, *J. Electroanal. Chem.*, **145**, 439 (1983).
- (33) C.K. Chang and I. Abdalmuhdi, *Angew. Chem. Int. Ed. Engl.*, **23**, 164 (1984).
- (34) C.K. Chang, H.Y. Liu and I. Abdalmuhdi, *J. Am. Chem. Soc.*, **106**, 2725 (1984).
- (35) H.-Y. Liu, I. Abdalmuhdi, C.K. Chang and F.C. Anson, *J. Phys. Chem.*, **89**, 665 (1985).
- (36) R. Jasinski, *J. Electrochem. Soc.*, **112**, 526 (1965).
- (37) A. Kozawa, V.E. Zilionis and R.J. Brodd, *J. Electrochem. Soc.*, **117**, 1470 (1970).

- (38) A. Kozawa, V.E. Zillionis and R.J. Brodd, *J. Electrochem. Soc.*, **117**, 1474 (1970).
- (39) A. Kozawa, V.E. Zillionis and R.J. Brodd, *J. Electrochem. Soc.*, **118**, 1705 (1971).
- (40) J.-P. Randin, *Electrochim. Acta*, **19**, 83 (1974).
- (41) J. Zagal, R.K. Sen and E. Yeager, *J. Electroanal. Chem.*, **83**, 207 (1977).
- (42) J. Zagal, P. Bindra and E. Yeager, *J. Electrochem. Soc.*, **127**, 1506 (1980).
- (43) F. van den Brink, W. Visscher and E. Barendrecht, *J. Electroanal. Chem.*, **157**, 283 (1983).
- (44) F. van den Brink, W. Visscher and E. Barendrecht, *J. Electroanal. Chem.*, **157**, 305 (1983).
- (45) F. van den Brink, W. Visscher and E. Barendrecht, *J. Electroanal. Chem.*, **172**, 301 (1984).
- (46) F. van den Brink, W. Visscher and E. Barendrecht, *J. Electroanal. Chem.*, **175**, 279 (1984).
- (47) J.H. Zagal, M. Paez, J. Sturm and S. Ureta-Zanartu, *J. Electroanal. Chem.*, **181**, 295 (1984).
- (48) T. Osaka, K. Naoi, T. Hirabayashi and S. Nakamura, *Bull. Chem. Soc. Jpn.*, **59**, 2717 (1986).
- (49) A. Elzing, A. van der Putten, W. Visscher and E. Barendrecht, *J. Electroanal. Chem.*, **200**, 313 (1986).

- (50) A. van der Putten, A. Elzing, W. Visscher and E. Barendrecht, *J. Electroanal. Chem.*, 214, 523 (1986).
- (51) D. Wohrle, *Fortschr. Hochpolym. Forsch.*, 10, 35 (1972).
- (52) M. Savy, P. Andro, C. Bernard and G. Magner, *Electrochim. Acta*, 18, 191 (1973).
- (53) M. Savy, P. Andro and C. Bernard, *Electrochim. Acta*, 19, 403 (1974).
- (54) A.J. Appleby and M. Savy, *Natl. Bur. Stand. (U.S.), Spec. Publ.*, 455, 241 (1976).
- (55) A.J. Appleby, J. Fleisch and M. Savy, *J. Catal.*, 44, 281 (1976).
- (56) S. Marole, M. Savy and J.J. Verbist, *Inorg. Chem.*, 18, 2560 (1979).
- (57) L. Kreja and A. Pliewka, *Electrochim. Acta*, 25, 1283 (1980).
- (58) H. Behret, H. Binder, G. Sandstedt and G.G. Scherer, *J. Electroanal. Chem.*, 117, 29 (1981).
- (59) J. Blomquist, U. Helgeson and L.C. Moberg, *Electrochim. Acta*, 27, 1445 (1982).
- (60) J. Blomquist, U. Helgeson and L.C. Moberg, *Electrochim. Acta*, 27, 1453, (1982).
- (61) L. Kreja, *Electrochim. Acta*, 28, 1807 (1983).
- (62) T. Hirai and J.-I. Yamaki, *J. Electrochem. Soc.*, 132, 2125 (1986).

- (63) C.C. Leznoff, S. Greenberg, S.M. Marcuccio, P.C. Minor, P. Seymour and A.B.P. Lever, *Inorg. Chim. Acta*, **89**, L35 (1984).
- (64) C.C. Leznoff, S.M. Marcuccio, S. Greenberg, A.B.P. Lever and K.B. Tomer, *Can. J. Chem.*, **63**, 623 (1985).
- (65) S.M. Marcuccio, P.I. Svirskaya, S. Greenberg, A.B.P. Lever and C.C. Leznoff, *Can. J. Chem.*, **63**, 3057 (1985).
- (66) E.S. Dodsworth, A.B.P. Lever, P. Seymour and C.C. Leznoff, *J. Phys. Chem.*, **89**, 5698 (1985).
- (67) W.A. Nevin, W. Liu and A.B.P. Lever, *Can. J. Chem.*, **65**, 855, (1987).
- (68) M. Gouterman, "The Porphyrins", D. Dolphin, Ed., Vol. III, pt. A, Academic Press, New York, 1978, p. 1.
- (69) S. Greenberg, S.M. Marcuccio, C.C. Leznoff and K.B. Tomer, *Synthesis*, 406 (1986).
- (70) The cathodic waves for these couples were deconvoluted by subtracting the background from a neat DCB solution to obtain a baseline followed by construction of a symmetric wave about the peak of couple I. The contribution of the symmetric wave in the region of mixed currents was subtracted from the observed response to obtain the current associated with couple II. Complete details of this deconvolution are described in: M.R. Hempstead, Ph.D.

Thesis, York University, 1987.

- (71) A.J. Bard and L.R. Faulkner, "Electrochemical Methods",
John Wiley & Sons, New York, 1980.
- (72) R.H. Wopschall and I. Shain, Anal. Chem., 39, 1514 (1967).
- (73) W.A. Nevin, M.R. Hempstead, W. Liu, C.C. Leznoff and
A.B.P. Lever, Inorg. Chem., 26, 570, (1987).
- (74) J.H. Zagal, Ph.D. Thesis, Case Western Reserve University,
1978.
- (75) A.N. Frumkin, Z. Phys., 35, 792 (1926).
- (76) E. Laviron, J. Electroanal. Chem., 52, 395 (1974).
- (77) J. Schreurs and E. Barendrecht, Recl. Trav. Chim. Pays-
Bas, 103, 205 (1984).
- (78) P. Nikitas, J. Chem. Soc., Faraday Trans. 1, 81, 1767
(1985).
- (79) A.N. Frumkin and B.B. Damaskin, Pure Appl. Chem., 15, 263
(1967).
- (80) A.B.P. Lever, M.R. Hempstead, C.C. Leznoff, W. Liu, M.
Melnik, W.A. Nevin and P. Seymour, Pure Appl. Chem., 58,
1467 (1986).
- (81) A.P. Brown, C. Koval and F.C. Anson, J. Electroanal.
Chem., 72, 379 (1976).
- (82) J. Newman, J. Phys. Chem., 70, 1327 (1966).

- (83) W.F. Linke, "Solubilities of Inorganic and Metal Organic Compounds", Vol. II, 4th ed., Amer. Chem. Soc., Washington, D.C., 1965, p. 1219.
- (84) "Handbook of Chemistry and Physics", R.C. Weast, Ed., 57th ed., CRC Press, Cleveland, 1977.
- (85) J. Koutecky and V.G. Levich, Zh. Fiz. Khim., 32, 1565 (1957).
- (86) "Studies in Soviet Science: The Rotating Disc Electrode", Yu.V. Pleskov and V.Yu. Filinovski, Eds., Consultants Bureau, New York, 1976, p. 90.
- (87) P.N. Ross and P.C. Andricacos, J. Electroanal. Chem., 154, 205 (1983).
- (88) F. Opekar and P. Beran, J. Electroanal. Chem., 69, 1 (1976).
- (89) K. Shigehara and F.C. Anson, J. Phys. Chem., 86, 2776 (1982).
- (90) A. Frumkin and G. Tedoradse, Z. Elektrochem., 62, 251 (1958).
- (91) T.E. Mallouk, V. Cammarata, J.A. Crayson and M.S. Wrighton, J. Phys. Chem., 90, 2150 (1986).
- (92) C.C. Leznoff, H. Lam, S.M. Marcuccio, W.A. Nevin, P. Janda, N. Kobayashi and A.B.P. Lever, J. Chem. Soc., Chem. Commun., 699 (1987).

Figure Legends

Figure 1 Cyclic voltammograms at scan rates of a) 50 mV/s, b) 100 mV/s, and c) 150 mV/s for 2.5×10^{-5} M CoTNPc in DCB and 0.1 M TBAP under argon at a SAPG working electrode. Couples I and II are both associated with the $[\text{Co(II)TNPc(-1)}]^+/\text{Co(II)TNPc(-2)}$ process. The nature of these couples is investigated more fully in Figure 2.

Figure 2 Plots of the dependence of cathodic peak current with scan rate for A) couple I and B) couple II, as designated in Figure 1. (2.5×10^{-5} M CoTNPc in DCB and 0.1 M TBAP at a SAPG working electrode).

Figure 3 Cyclic voltammograms at scan rates of a) 50 mV/s, b) 100 mV/s, and c) 150 mV/s for 1.0×10^{-5} M TNPcCo in DCB and 0.1 M TBAP at an OPG working electrode. The waves shown here are associated with the $[\text{Co(II)TNPc(-1)}]^+/\text{Co(II)TNPc(-2)}$ couple.

Figure 4 Cyclic voltammograms displaying adsorption features of a) O(1)[TNPcCo]_2 , b) Cat(4)[TNPcCo]_2 , c) C(2)[TNPcCo]_2 , and d) $\text{EtMeO(5)[TNPcCo]}_2$. All voltammograms were recorded at a scan rate of 100 mV/s for a binuclear concentration of ca. 5 μM in DCB and 0.1 M TBAP. The waves shown here are associated with the $[\text{Co(II)TNPc(-1)}]^+/\text{Co(II)TNPc(-2)}$ couple.

Figure 5 Levich plot of the diffusion-limited O_2 reduction current at a CoTNPC-modified OPG electrode. The dashed line is the response predicted by equation [6] and the solid line is the fit through the experimental data denoted by + 's.

Figure 6 Reduction of molecular oxygen at a rotating OPG electrode modified CoTNPC in an O_2 saturated 0.10 M NaOH solution.

Figure 7 Koutecky-Levich plots for the reduction of molecular oxygen in 0.10 M NaOH at -0.450 V versus SCE on OPG electrodes modified with $\square$ CoTNPC, $+$ O(1)[CoTrNPc] $_2$, $+$ C(2)[CoTrNPc] $_2$, Δ Cat(4)[CoTrNPc] $_2$, or $\times$ EtMeO(5)[CoTrNPc] $_2$. A theoretical two electron line is shown at the bottom of the graph for comparison.

Compound	θ	$r\Gamma$
CoTNPc	1.4 ± 0.4	-0.77 ± 0.14
O(1)[CoTrNPc] ₂	1.3 ± 0.4	-1.36 ± 0.11
C(2)[CoTrNPc] ₂	1.8 ± 0.1	-0.87 ± 0.13
Cat(4)[CoTrNPc] ₂	2.2 ± 0.2	-0.88 ± 0.06
EtMeO(5)[CoTrNPc] ₂	2.2 ± 0.4	-0.85 ± 0.01

Table 1 Average values of θ and $r\Gamma$ for an OPG electrode modified with CoTNPc or one of its binuclear derivatives.

Compound	Half-Bandwidths (cm ⁻¹)	
	Co(III)	Co(I)
CoTNPc	680	660
C(2)[CoTrNPc] ₂	765	735
Cat(4)[CoTrNPc] ₂	800	775
EtMeO(5)[CoTrNPc] ₂	785	775
O(1)[CoTrNPc] ₂	1000	920


Table 2 Half-bandwidths of the O band for CoTNPc and its binuclear derivatives as Co(III) and also as Co(I). These half-bandwidths were calculated from the spectra obtained by bulk electrolysis of DCB solutions containing these species along with an excess of tetrabutylammoniumhydroxide and 0.1 M TBAP [80].



Compound	n			
	Potential (Volts versus SCE)			
	-0.450	-0.500	-0.550	-0.600
CoTNPC	1.94±0.17	1.93±0.11	1.91±0.10	1.93±0.06
O(1)[CoTrNPC] ₂	2.07±0.02	2.04±0.02	2.02±0.02	2.01±0.01
C(2)[CoTrNPC] ₂	2.09±0.01	2.05±0.01	2.01±0.01	1.99±0.02
Cat(4)[CoTrNPC] ₂	2.10±0.09	2.03±0.01	1.99±0.01	1.98±0.02
EtMeO(5)[CoTrNPC] ₂	1.94±0.01	1.94±0.02	1.94±0.01	1.96±0.01

Table 3 Average values of n for the electrocatalytic reduction of oxygen in 0.10 M NaOH at an OPG electrode modified with CoTNPC or one of its binuclear derivatives.


Compound	Potential (Volts versus SCE)				Average Normalized i_k
	-0.450	-0.500	-0.550	-0.600	
CoTNPC	1.51 (1)	3.00 (1)	5.58 (1)	9.95 (1)	-
C(2)[CoTrNPC] ₂	1.64 (1.09)	3.20 (1.07)	5.90 (1.06)	11.01 (1.11)	1.08±0.02
Cat(4)[CoTrNPC] ₂	1.84 (1.22)	3.91 (1.30)	7.95 (1.42)	16.01 (1.61)	1.39±0.17
EtMeO(5)[CoTrNPC] ₂	2.35 (1.56)	4.38 (1.46)	7.68 (1.38)	13.08 (1.31)	1.43±0.10
O(1)[CoTrNPC] ₂	2.45 (1.62)	4.61 (1.54)	8.15 (1.46)	13.89 (1.40)	1.50±0.10


Table 4 Kinetic currents, in mA, and normalized kinetic currents (in brackets) for oxygen reduction in 0.10 M NaOH at OPG electrodes modified with CoTNPC or one of its binuclear derivatives. (Electrode area = 0.493 cm²)

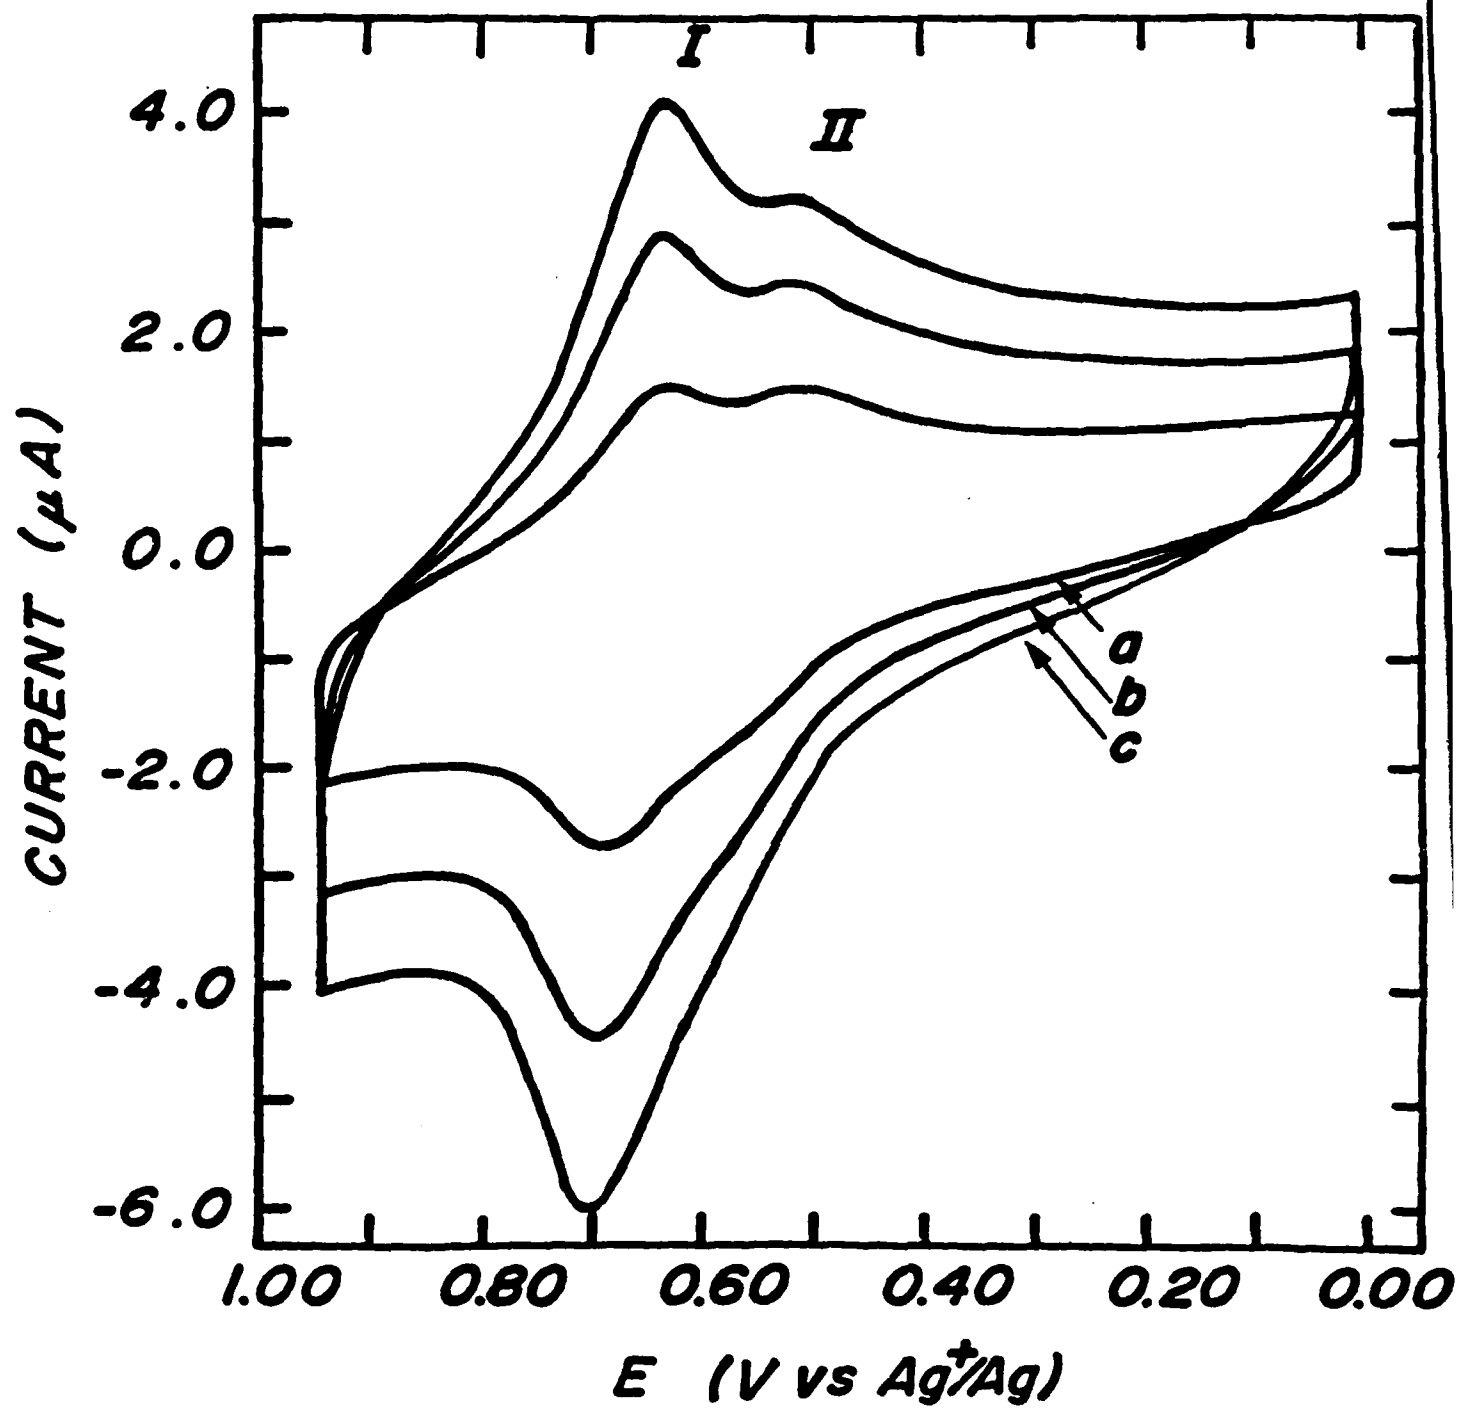


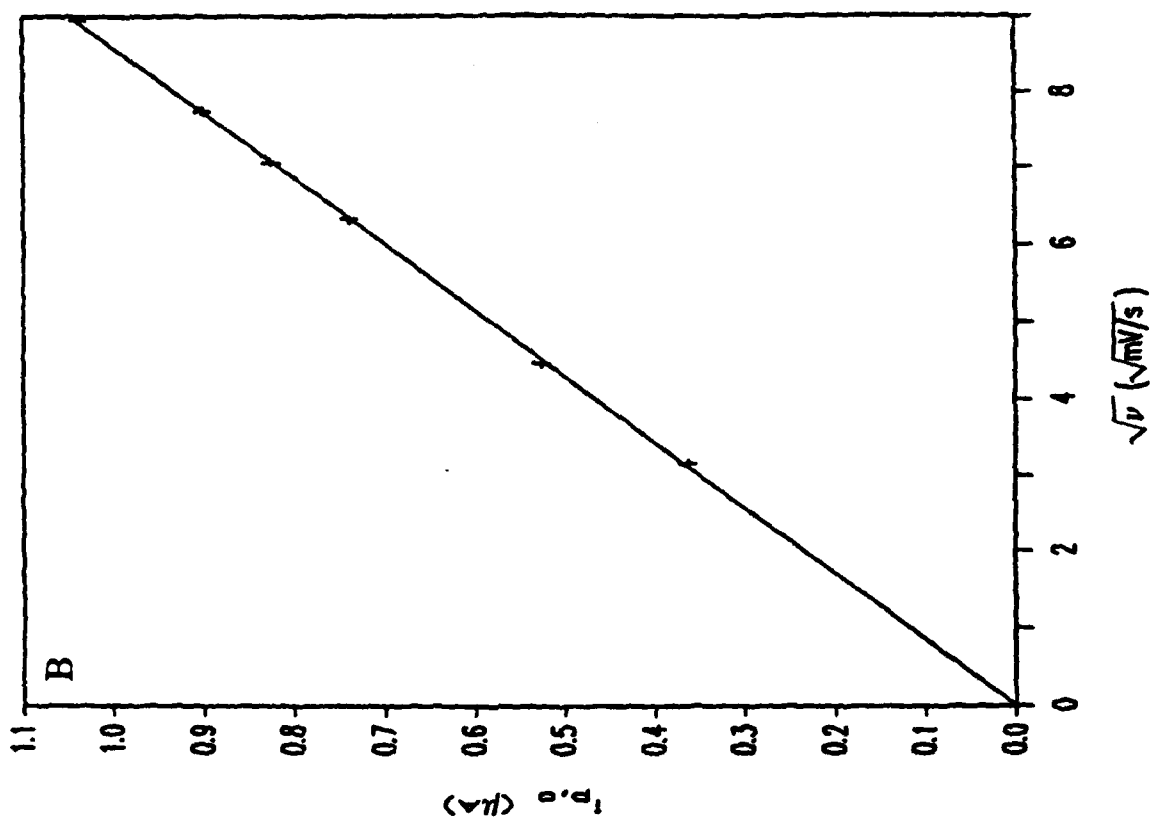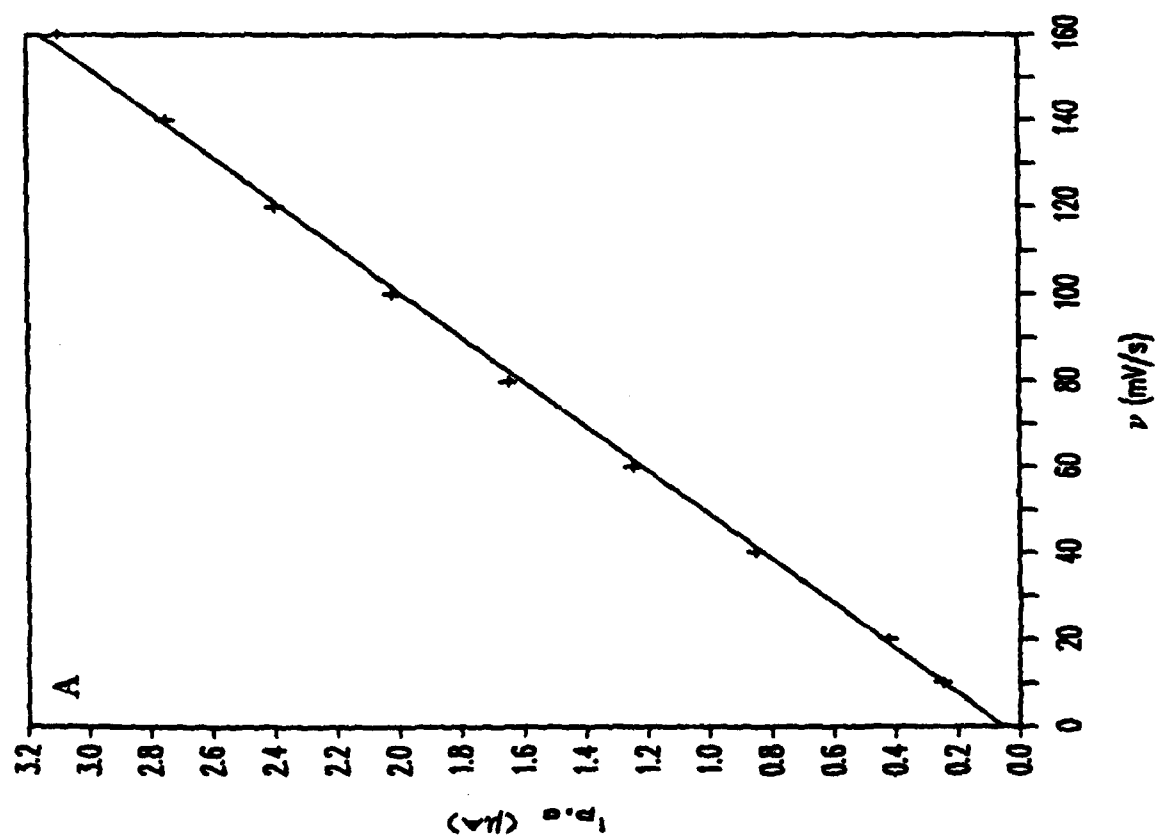



337

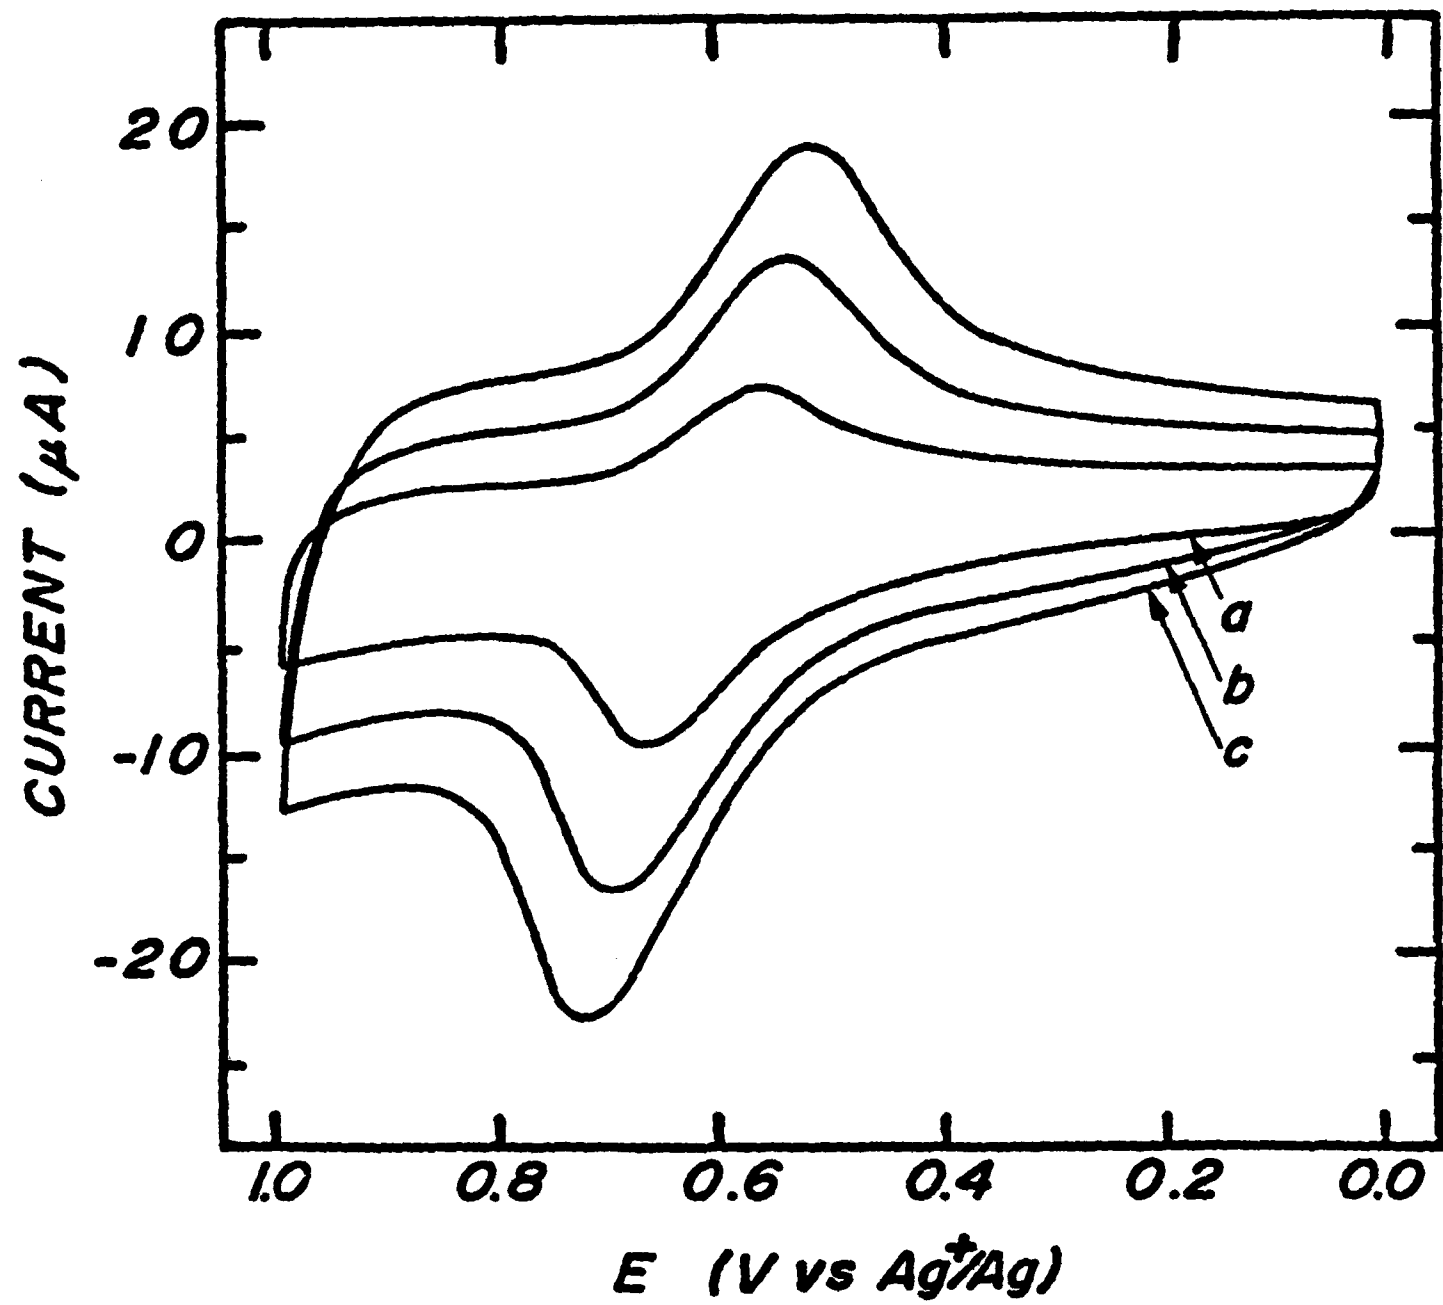

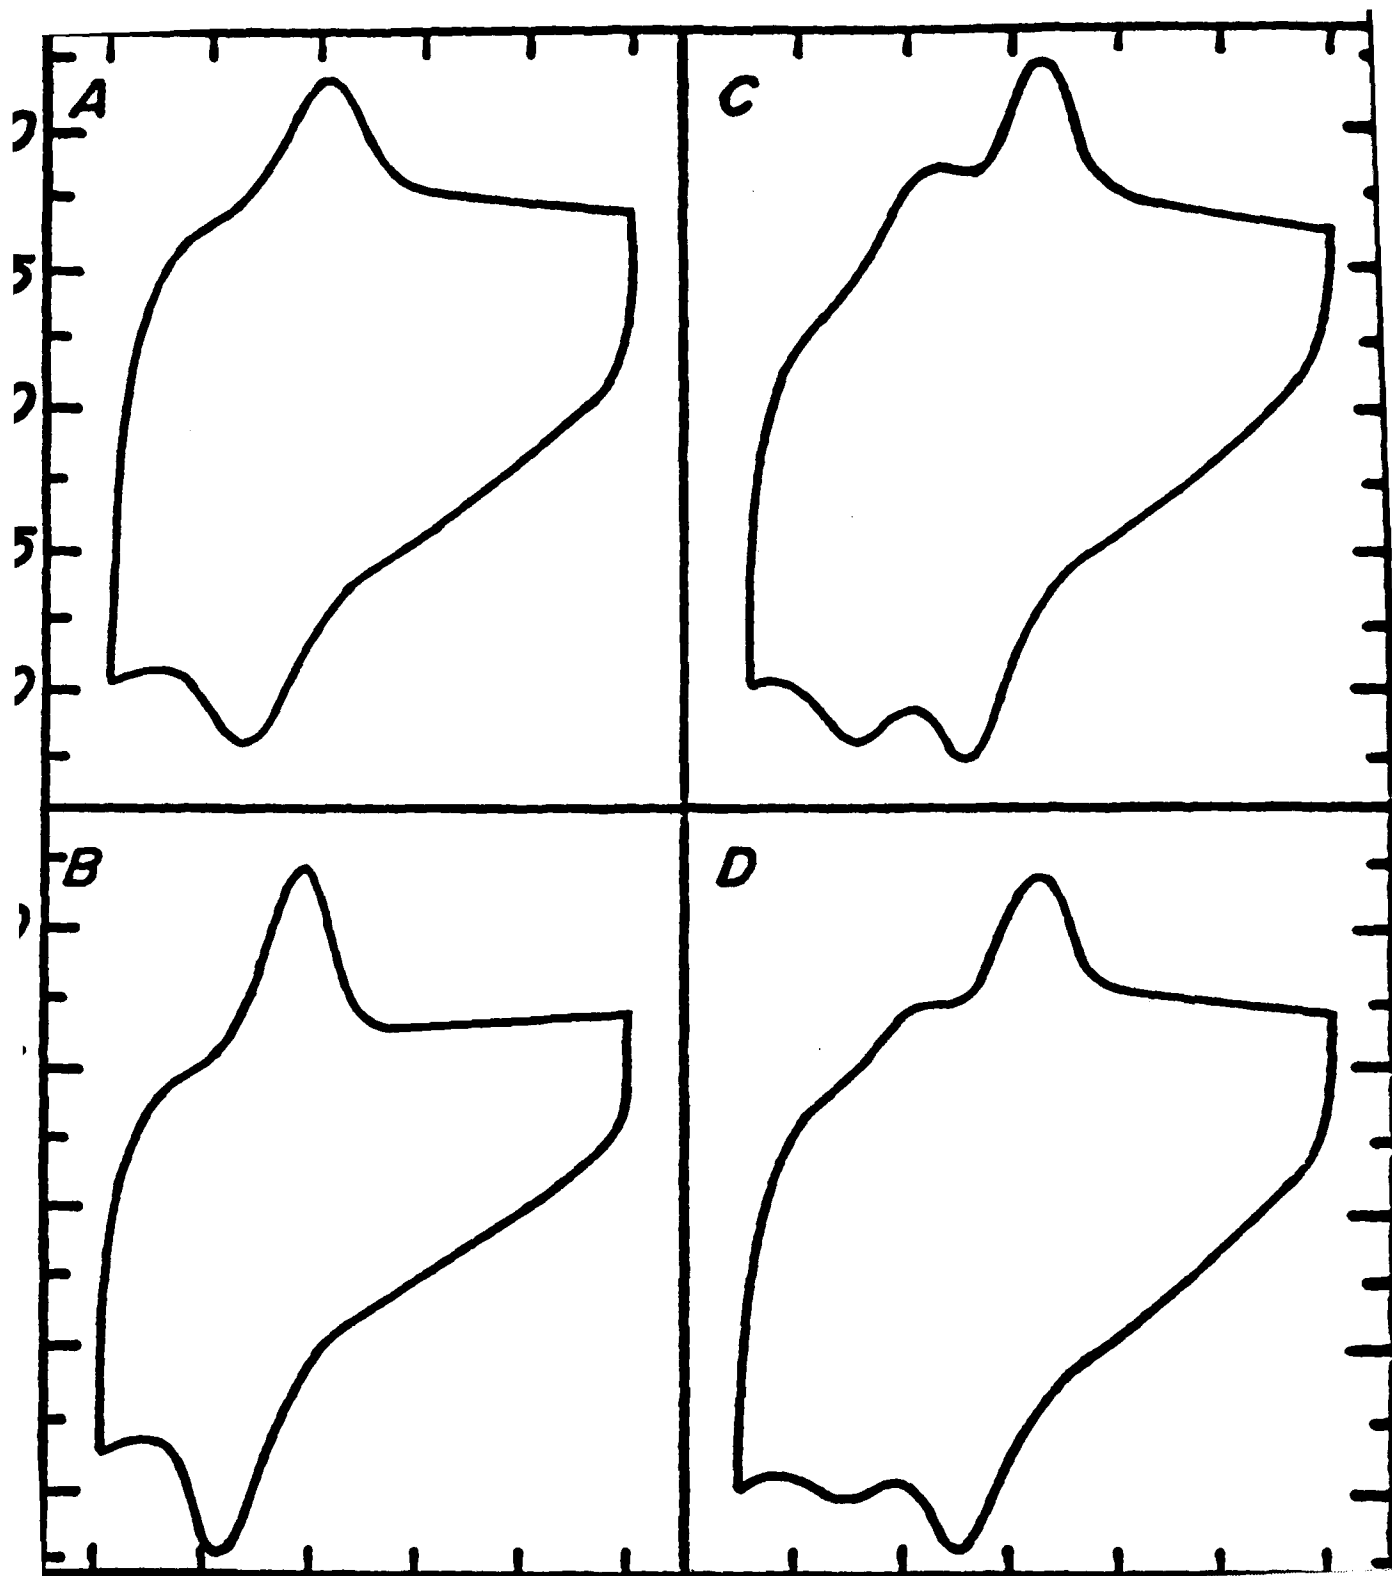

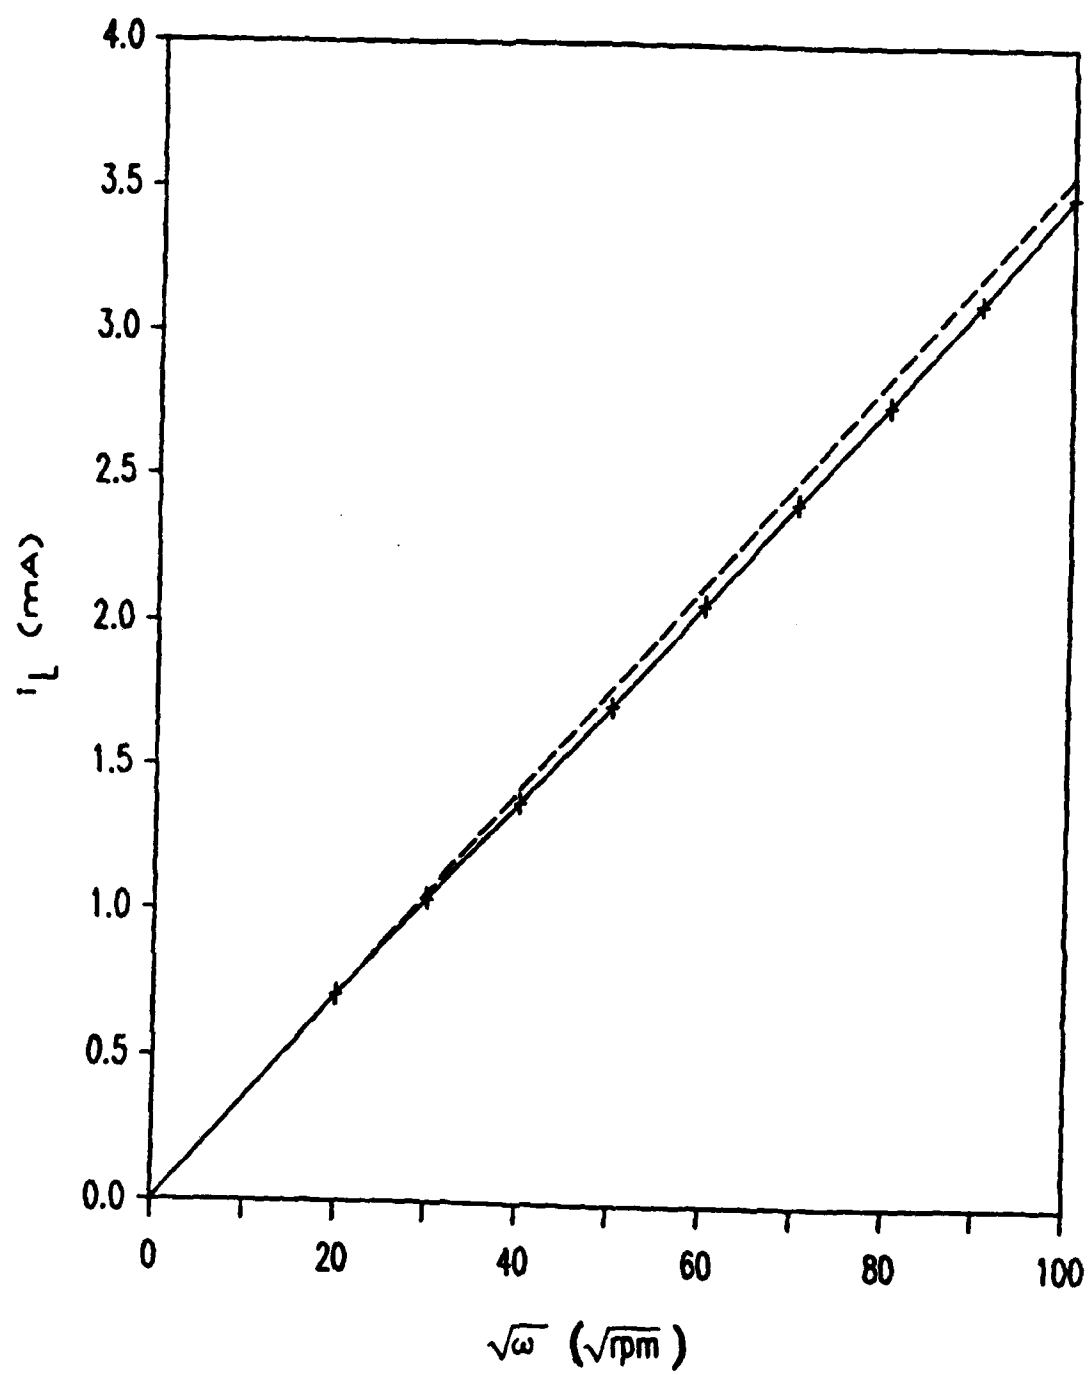

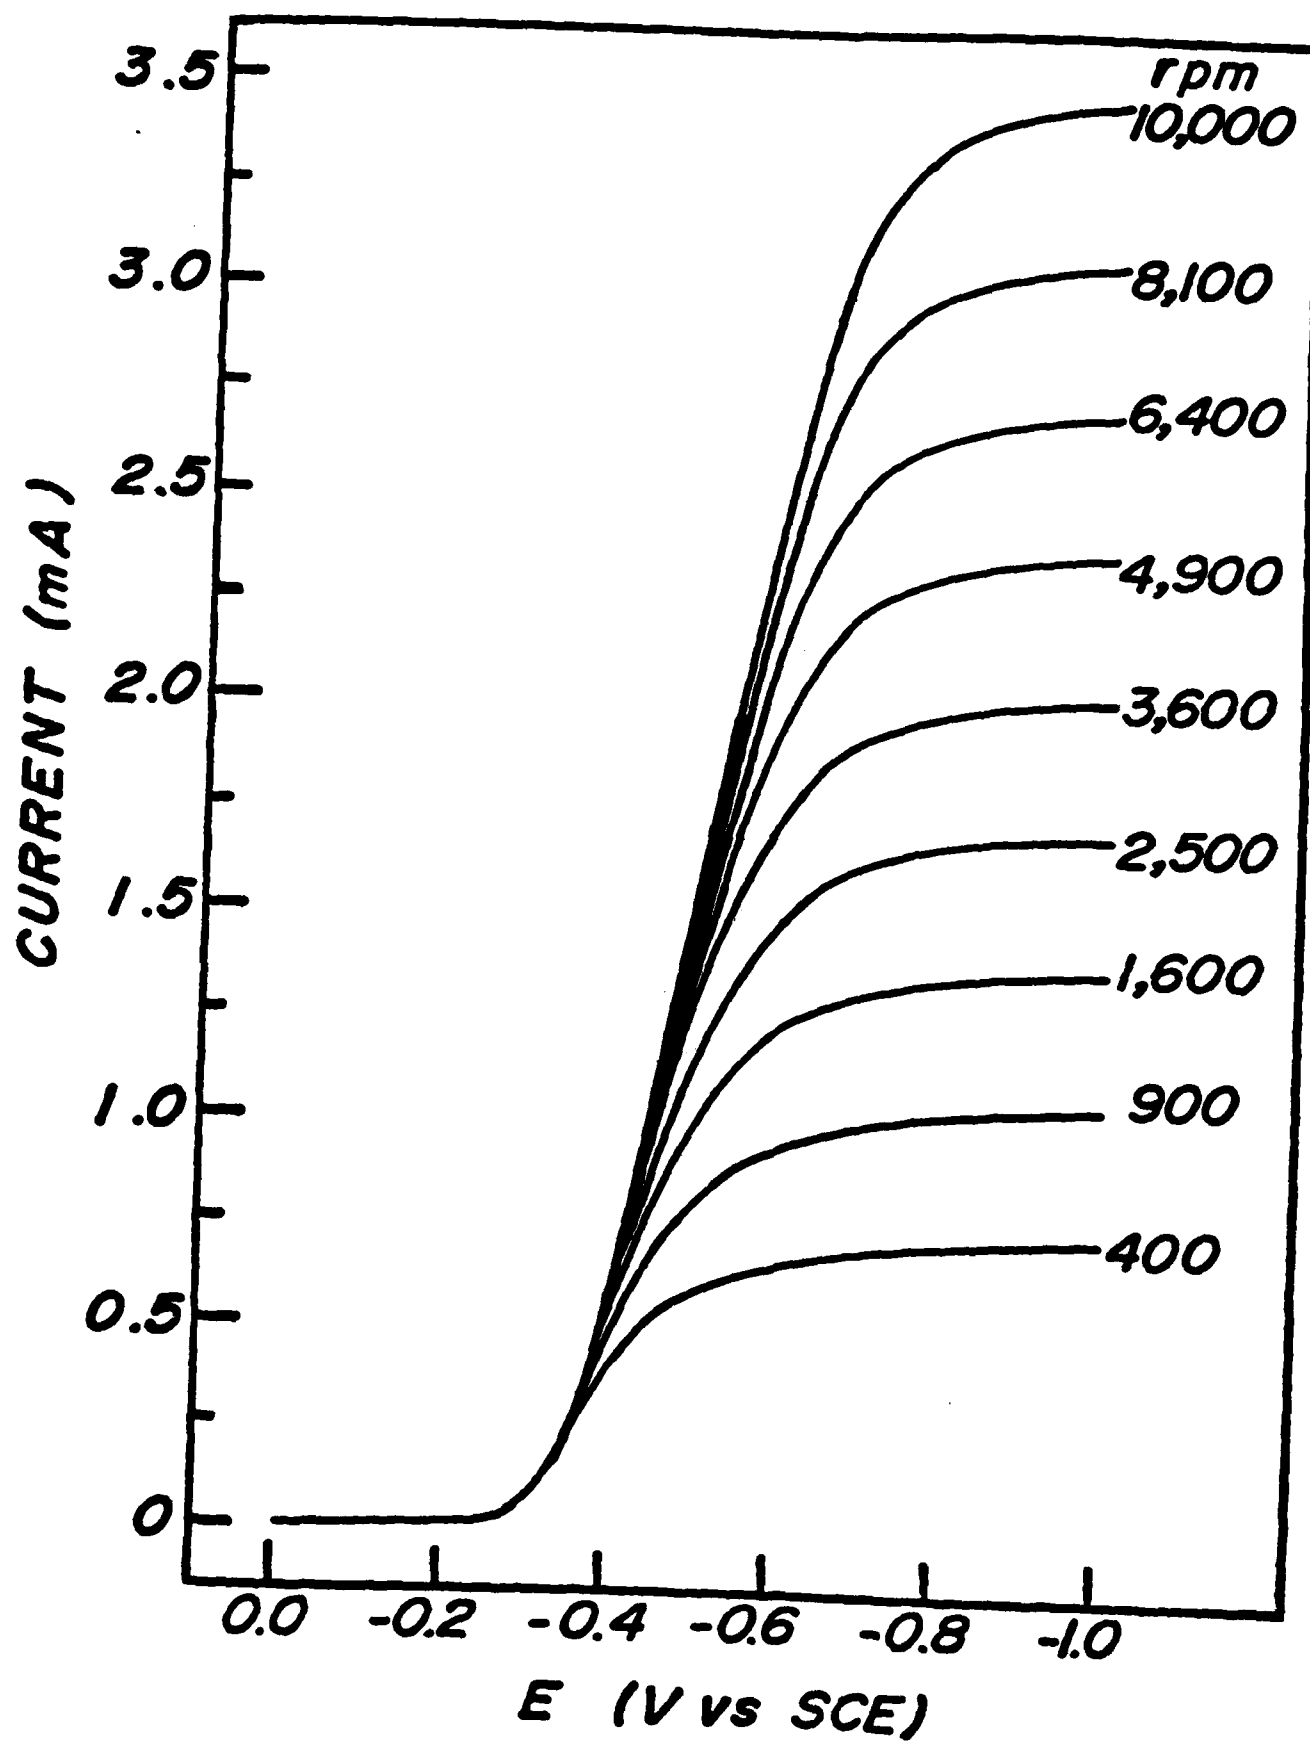

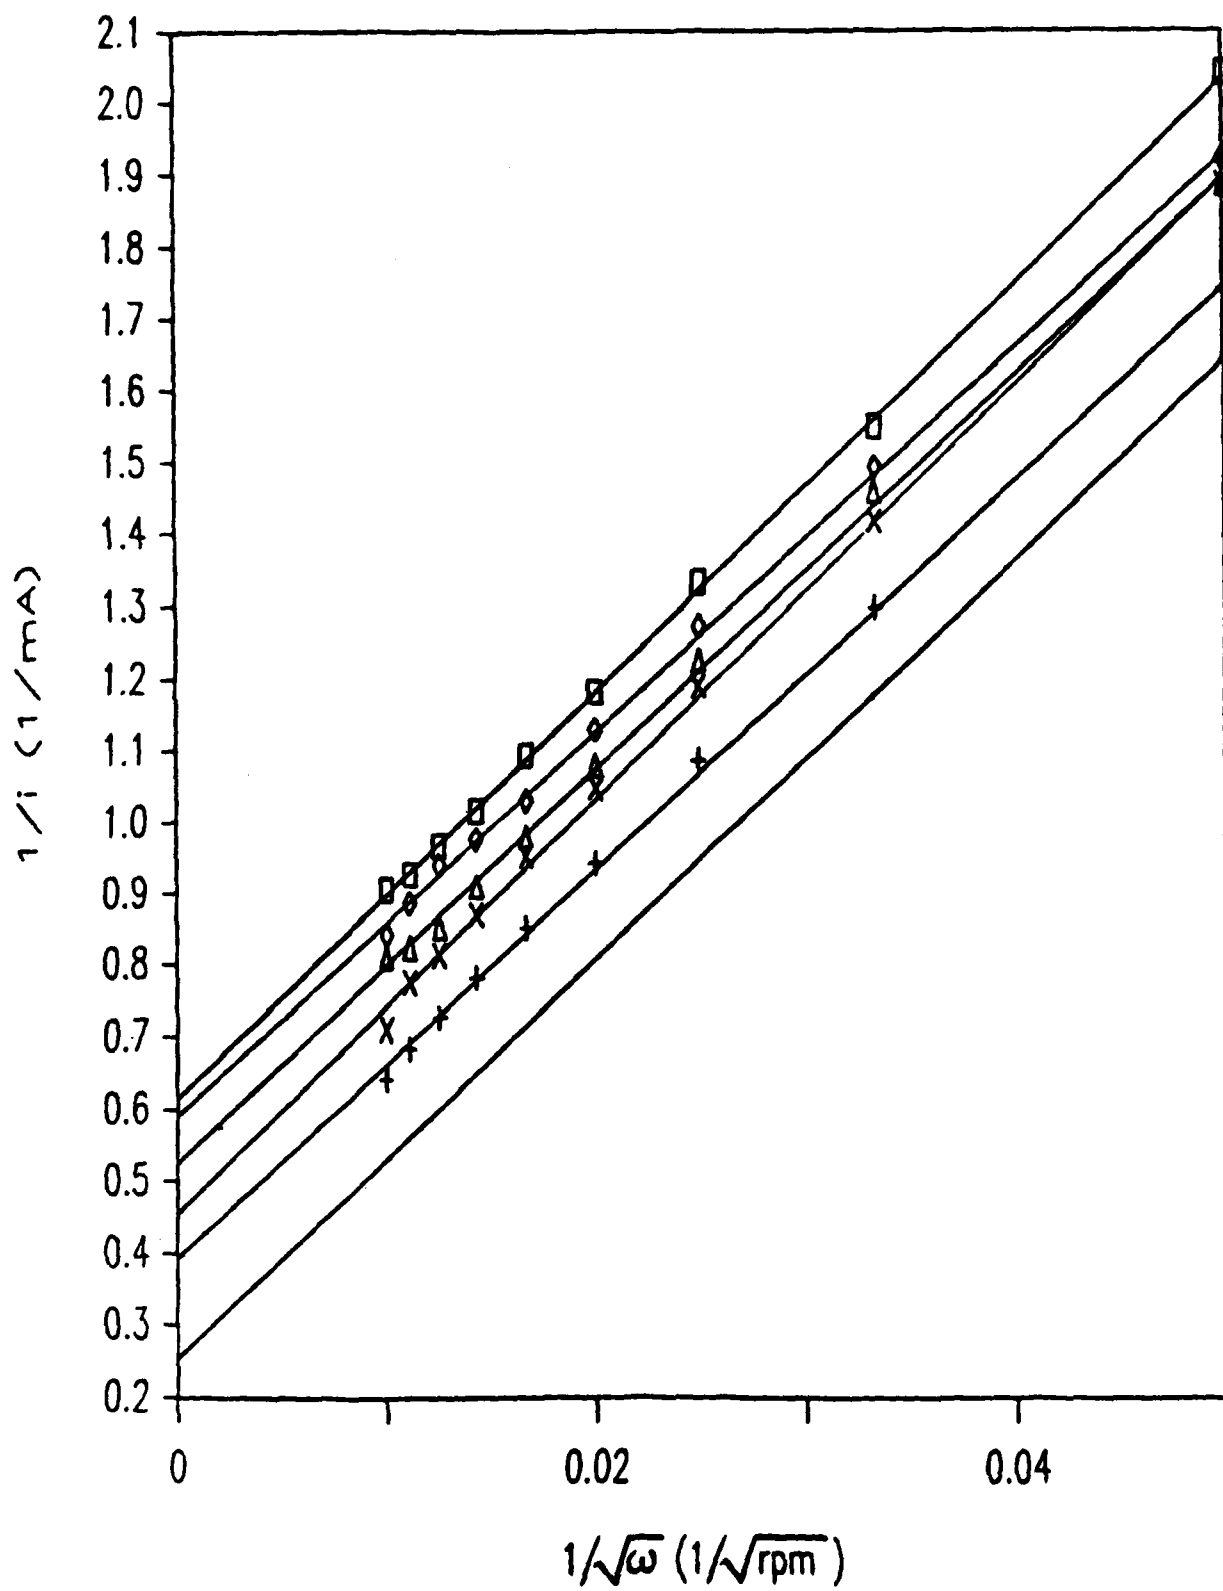

END

DATE
FILMED

DEC.

1987