

AD-A188 282

PREPARATION AND CHARACTERIZATION OF CO(II)/ZRO2 SOLID
SOLUTION(U) BROWN UNIV PROVIDENCE RI DEPT OF CHEMISTRY
P HU ET AL. 27 OCT 87 TR-9 N00014-86-K-0234


1/1

UNCLASSIFIED

F/G 7/2

NL



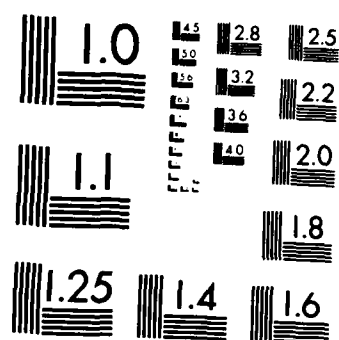

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

OFFICE OF NAVAL RESEARCH

CONTRACT N00014-86-K-0234

TECHNICAL REPORT No. 9

Preparation and Characterization of Co(II)/ZrO₂ Solid Solution

by

Ping Wu, Robert Kershaw, Kirby Dwight and Aaron Wold

Prepared for Publication

in the

Materials Research Bulletin



Brown University
Department of Chemistry
Providence, RI 02912

October 27, 1987

Reproduction in whole or in part is permitted for
any purpose of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited.

AD-A188 202

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION UNCLASSIFIED			1d. RESTRICTIVE MARKINGS		
2a. SECURITY CLASSIFICATION AUTHORITY			3. DISTRIBUTION/AVAILABILITY OF REPORT APPROVED FOR PUBLIC RELEASE: DISTRIBUTION UNLIMITED		
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE					
4. PERFORMING ORGANIZATION REPORT NUMBER(S) # 9			5. MONITORING ORGANIZATION REPORT NUMBER(S) N00014-86 K 0234		
6a. NAME OF PERFORMING ORGANIZATION AARON WOLD BROWN UNIVERSITY		6b. OFFICE SYMBOL (If applicable)	7a. NAME OF MONITORING ORGANIZATION OFFICE OF NAVAL RESEARCH DR. DAVID NELSON		
6c. ADDRESS (City, State, and ZIP Code) CHEMISTRY DEPARTMENT PROVIDENCE RI 02912			7b. ADDRESS (City, State, and ZIP Code) CODE 472 800 N. QUINCY STREET ARLINGTON, VA 22217		
8a. NAME OF FUNDING/SPONSORING ORGANIZATION		8b. OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER		
8c. ADDRESS (City, State, and ZIP Code)			10. SOURCE OF FUNDING NUMBERS		
			PROGRAM ELEMENT NO	PROJECT NO	TASK NO
			WORK UNIT NO		
11. TITLE (include Security Classification) PREPARATION AND CHARACTERIZATION OF Co(II)/ZrO₂ SOLID SOLUTION					
12. PERSONAL AUTHOR(S)					
13a. TYPE OF REPORT TECHNICAL		13b. TIME COVERED FROM TO		14. DATE OF REPORT (Year, Month, Day) OCTOBER 27, 1987	
15. PAGE COUNT					
16. SUPPLEMENTARY NOTATION ACCEPTED FOR PUBLICATION IN MATERIALS RESEARCH BULLETIN					
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)		
FIELD	GROUP	SUB-GROUP			
19. ABSTRACT (Continue on reverse if necessary and identify by block number) Samples of cubic ZrO₂ containing up to almost 10 atomic percent cobalt were prepared by codecomposition of the nitrate. Magnetic susceptibility measurements confirmed the limit of solubility and the presence of cobalt as Co(II). The reduction of the cobalt inserted in cubic zirconia took place at a considerably higher temperature than bulk cobalt oxide.					
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT ☐ UNCLASSIFIED UNLIMITED ☐ SAME AS RPT ☐ DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION		
22a. NAME OF RESPONSIBLE INDIVIDUAL			22b. TELEPHONE (include Area Code)		22c. OFFICE SYMBOL



PREPARATION AND CHARACTERIZATION OF Co(II)/ZrO₂ SOLID SOLUTION

by

Ping Wu, Robert Kershaw, Kirby Dwight and Aaron Wold*
Department of Chemistry, Brown University
Providence, RI 02912

*Address all correspondence

A-1

ABSTRACT

Samples of cubic ZrO₂ containing up to almost 10 atomic percent cobalt were prepared by codecomposition of the nitrate. Magnetic susceptibility measurements confirmed the limit of solubility and the presence of the cobalt as Co(II). The reduction of the cobalt inserted in cubic zirconia took place at a considerably higher temperature than bulk cobalt oxide.

MATERIALS INDEX: Cobalt stabilized cubic ZrO₂.

Introduction

Cubic ZrO₂ samples containing some transition metal oxides including rhodium oxide (1), iron oxide (2), chromium oxide (3) and nickel oxide (4) were studied previously in this laboratory. Their structures, magnetic properties and the stabilities towards reduction have been studied. There is little published data concerning the properties of the members in the cobalt oxide-zirconium oxide system. Structural studies of the supported Co(II)/ZrO₂ catalysts were carried out by Bettman and Yao (5, 6). Their samples were prepared by incipient wetness methods and the crystal structure of the products indicated the presence of monoclinic ZrO₂. Previous work has indicated that the presence of monoclinic ZrO₂ is characteristic of an absence of reaction between the ZrO₂ support and the catalyst.

It is the purpose of this work to investigate the formation of solid solution between ZrO₂ and cobalt oxide and to study the magnetic properties of such a system. In addition, the stability towards reduction of cubic ZrO₂ samples containing various concentrations of reacted cobalt oxide will be determined.

Experimental

Bulk cobalt oxide samples were prepared by decomposition of Co(NO₃)₃·9H₂O. The nitrate was dissolved in water and dried at 150°C for 12 hours. The samples were then ground and decomposed at temperatures ranging from 500°C to 800°C. X-ray analysis of the final products indicated the formation of Co₃O₄.

Zirconium oxide samples, containing various percentages of cobalt, were prepared by dissolving the desired quantity of analyzed cobalt nitrate $\text{Co}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ with appropriate amounts of $\text{ZrO}(\text{NO}_3)_2$. Two ml of water were added for each millimole of total nitrates. The solution was then dried at 150°C for 12 hours and the product was ground and heated at 500°C for 24 hours. Some samples were then subsequently heated at elevated temperatures between 500 - 800°C . In order to ascertain the temperatures for complete decomposition of the nitrates, preliminary decomposition experiments were carried out in a Cahn system 113 thermal balance.

X-ray powder diffraction patterns of the samples were obtained using a Philips diffractometer and monochromated high intensity $\text{CuK}\alpha_1$ radiation ($\lambda = 1.5405\text{\AA}$). For qualitative identification of the phases present, the diffraction patterns were taken in the range $12^\circ < 2\theta < 80^\circ$ with a scan rate of $1^\circ 2\theta/\text{min}$ and a chart speed of 30 inches/hr. The scan rate used to obtain x-ray patterns for calculation of cell parameters was $0.25 2\theta/\text{min}$ with a chart speed of 30 in/hr. Cell parameters were obtained from a least squares refinement of the data with the aid of a computer program which corrected for the systematic experimental errors.

Magnetic susceptibilities were measured using a Faraday balance at a field strength of 10.4 kOe. Honda-Owens (field dependency) plots were also made and all magnetic susceptibility data were corrected for core diamagnetism. Magnetic susceptibility measurements were made from liquid nitrogen temperature to 315K.

Temperature programmed reductions were carried out in a thermal balance equipped with a magnet (7). The weight of the sample was determined using a Cahn electrobalance (model RG) alternately in a magnetic field gradient and without the magnetic field gradient. The temperature was measured by a type S thermocouple which was positioned just below the sample. This technique combines magnetic measurements with thermogravimetric analysis and is very sensitive to the appearance and growth of a magnetic phase during the reaction (7). An 85%Ar/15% H_2 mixture was predried by P_2O_5 and passed at a rate of 60 ml/min into the TGA balance. The samples were heated at 50°C per hour.

Results and Discussion

Bulk samples of cobalt oxide were prepared by the decomposition of $\text{Co}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ at temperatures ranging from 500°C to 800°C . X-ray diffraction analysis of the products indicated the presence of a single phase, namely Co_3O_4 . In order to analyze any deviation from stoichiometry, temperature programmed reduction was carried out by thermogravimetric analysis. The weight change in the process of T.P.R occurs between 230° and 320°C . The total observed weight change is 26.6%, whereas the calculated weight change of the reduction of Co_3O_4 to cobalt metal is 26.5%. These results indicate that the composition of bulk cobalt oxide prepared under these conditions is Co_3O_4 .

Samples of the cobalt-zirconium oxide system were prepared by the codecomposition of $\text{Co}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ and $\text{ZrO}(\text{NO}_3)_2$. X-ray analyses of products containing varying compositions are given in Table 1. All of the products reported in Table 1 were prepared at 500°C .

Decomposition of pure zirconyl nitrate resulted in the formation of tetragonal ZrO_2 containing a small quantity of monoclinic ZrO_2 . For the samples prepared by codecomposition of the nitrates, x-ray analysis indicated that ZrO_2 crystallized with a cubic structure even when only 5 atomic percent of cobalt was introduced into the ZrO_2 . This is consistent with previous reports (8) that the stabilization of cubic ZrO_2 requires the presence of a solid solution with cobalt oxide. Products containing up to 10 atomic percent of cobalt showed no evidence of bulk cobalt oxide in the x-ray diffraction patterns. However, it can be seen from Table 1 that there is a decrease in the cell parameter of the cubic ZrO_2 phase which is consistent with an increase in the cobalt content of

TABLE 1
IDENTIFICATION OF PHASES FORMED IN THE $\text{Co(II)}/\text{ZrO}_2$ SYSTEM

Composition (at% Co)	Phase(s)	X-ray Parameters	
		a	c/a
ZrO_2 = 0	Tetragonal ZrO_2 plus small amount amount monoclinic ZrO_2	5.081(3)	1.02
$\text{Co}/(\text{Co}+\text{Zr})$ = 5	Cubic ZrO_2	5.086(3)	
$\text{Co}/(\text{Co}+\text{Zr})$ = 10	Cubic ZrO_2	5.072(3)	
$\text{Co}/(\text{Co}+\text{Zr})$ = 15	Cubic ZrO_2 + Co_3O_4		

this phase. When attempts were made to prepare cubic zirconium oxide containing 15 atomic percent cobalt, bulk Co_3O_4 was evident in the x-ray diffraction patterns. The limit of solubility of cobalt in ZrO_2 is therefore below 15 percent.

A sample of ZrO_2 containing 5 atomic percent cobalt was heated to 600° , 700° and 800°C . The cubic zirconium oxide remains stable at 600°C but at 700°C lines of Co_3O_4 and tetragonal ZrO_2 appear in the diffraction patterns of the products. Finally the monoclinic structure is obtained as the temperature is raised from 700° to 800°C .

The reciprocal magnetic susceptibility versus temperature data for bulk Co_3O_4 (i.e. $\text{Co(II)[Co(III)}_2\text{O}_4]$) is given in Fig. 1. The sample measured has a moment of 4.8 BM per Co(II) , since low-spin Co(III) is diamagnetic. This is consistent with the value reported in the literature (9). Strong spin-orbit coupling is a characteristic of Co(II) , which usually does not show a spin-only moment.

Magnetic measurements were also made on zirconium oxide samples containing 5 and 10 atomic percent cobalt. These measurements were made as functions of both

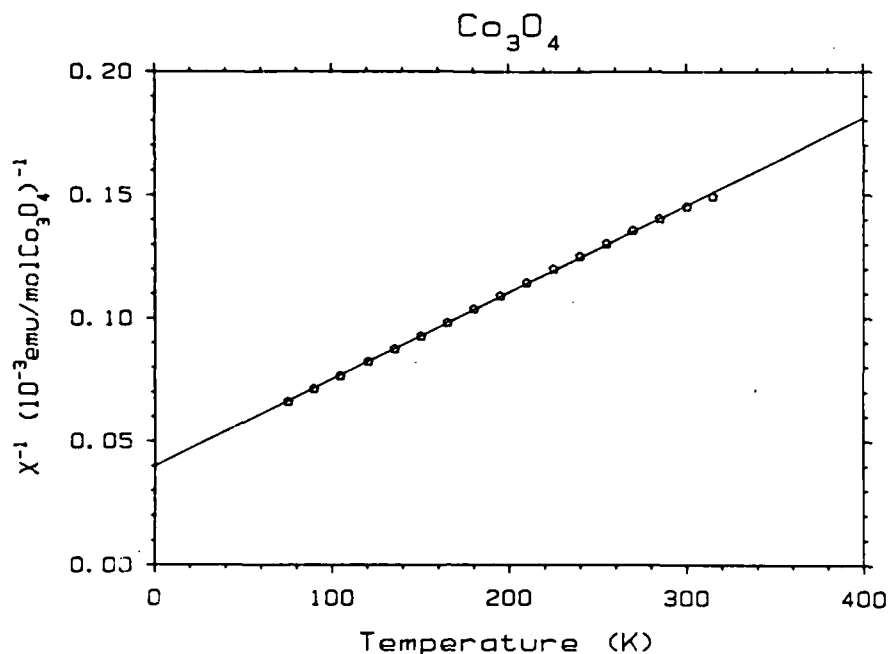


Fig. 1. Reciprocal magnetic susceptibility versus temperature data for bulk Co_3O_4 heated at 500°C for 24 hours.

field and temperature. All samples showed paramagnetic behavior and have no field dependency at either room temperature or liquid nitrogen temperature. The results of the magnetic measurements are plotted in Fig. 2 as reciprocal susceptibility versus temperature. The measured paramagnetic moment for the sample containing 5 atomic percent cobalt is 4.8 BM and hence all of the cobalt present is Co(II) . The measured value for the paramagnetic moment per cobalt ion of the sample containing 10 atomic percent cobalt is 4.4 BM which may indicate the coexistence of a small quantity of bulk Co_3O_4 . Additional evidence to substantiate these results follow from the TPR studies.

The temperature programmed reduction studies were carried out in a 85% $\text{Ar}/15\%\text{H}_2$ atmosphere using a thermomagnetic balance. The onset of reduction was detected by the difference in sample weight with and without a magnetic field gradient and arises from the ferromagnetism of cobalt. In the case of bulk Co_3O_4 , cobalt metal begins to form at 270°C (Fig. 3), and the sample with 5 atomic percent cobalt in ZrO_2 begins to reduce at 540°C . The stability of cobalt oxide towards reduction is therefore greatly increased by forming solid solution with zirconium oxide.

TPR of the sample containing 10 atomic percent cobalt indicated that there were two kinds of cobalt present in the sample (Fig. 3). Most of the cobalt was reduced above 500°C whereas a small amount of the cobalt began to reduce at 280°C . Therefore most of the cobalt has been inserted into the ZrO_2 but a small amount remains as bulk cobalt oxide. This is consistent with the observed decrease of the paramagnetic moment for the 10 atomic percent sample compared to

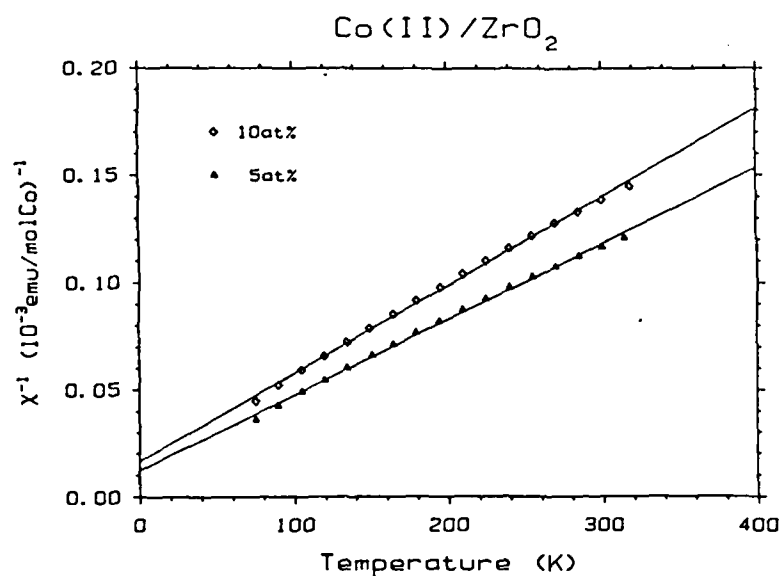


Fig. 2. Reciprocal magnetic susceptibility vs temperature for 5 and 10 at% Co(II)/ZrO₂ heated at 500°C for 24 hours.

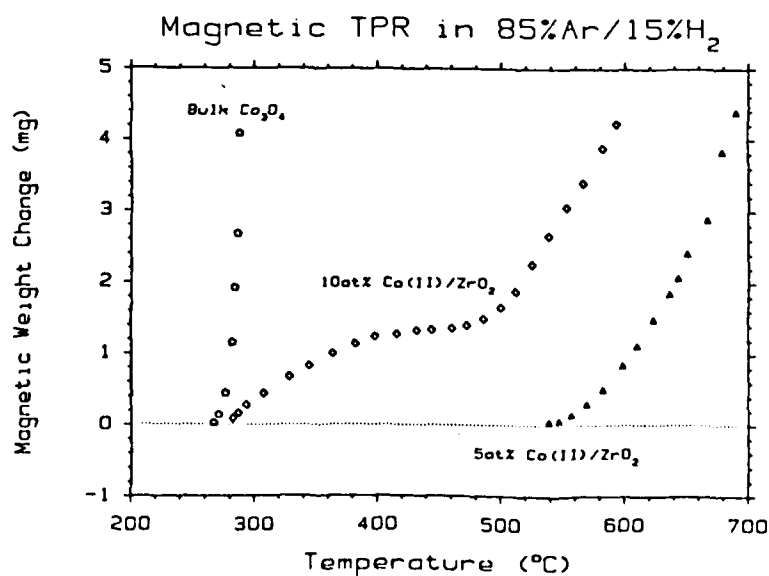


Fig. 3. Variation with temperature of the weight change caused by the application of a magnetic field gradient during the temperature programmed reduction of bulk Co₃O₄, 5 and 10 at% Co(II)/ZrO₂ in 85% Ar/15%H₂.

that obtained for the 5 atomic percent sample. The maximum solubility of cobalt oxide in zirconium oxide is therefore determined to be slightly lower than 10 atomic percent. It appears that codecomposition of the nitrates results in phases which contain cobalt (up to almost 10 atomic percent cobalt) as an integral part of the phase. However, it is only at 15 atomic percent that the presence of bulk cobalt oxide appears in the x-ray diffraction pattern. This is in contrast to the usual method of preparation, i.e. incipient wetness, in which the cobalt oxide is dispersed as a second phase on the ZrO_2 .

Acknowledgments

This research was partially supported by the Office of Naval Research and by the Exxon Education Fund. The authors also wish to acknowledge the support of the National Science Foundation, Grant No. DMR 820 3667, for the partial support of K. Dwight and the use of the Materials Research Laboratory at Brown University which is funded by the National Science Foundation.

References

1. Y-C. Zhang, K. Dwight and A. Wold, *Mat. Res. Bull.*, 21(7), 853 (1986).
2. S. Davison, R. Kershaw, K. Dwight and A. Wold, To be published in *J. Sol. St. Chem.*
3. P. Wu, R. Kershaw, K. Dwight and A. Wold. To be published in *J. Mat. Sci. Lett.*
4. K. E. Smith, R. Kershaw, K. Dwight and A. Wold. To be published in *Mat. Res. Bull.*
5. M. Bettman and H.C. Yao, "Materials Science Research" Vol. 10 Sintering and Catalysis. Ed. G. C. Kuczynski, New York 1975, page 165.
6. H. C. Yao and M. Bettman, *J. of Catal.*, 41, 349 (1976).
7. M. Schwartz, R. Kershaw, K. Dwight and A. Wold, *Mat. Res. Bull.*, 22(5), 609 (1987).
8. R. Collongues and J. Stocker, *Compt. Rend.* 246, 3641 (1958).
9. R. Perthel and H. Jahn, *Phys. Stat. Sol.* 5, 563 (1964).

Copy available to DTIC does not
 permit fully legible reproduction

Q/1113/86/2

ABSTRACTS DISTRIBUTION LIST, 05/19/59

Dr. J. E. Jensen Naval Research Laboratory 3011 Malibu Canyon Road Malibu, California 90265	Dr. R. Reeves Chemistry Department Consolidated Polymer Institute Troy, New York 12180
Dr. J. M. Weaver Department of Chemical Engineering University of Minnesota Minneapolis, Minnesota 55455	Dr. Steven R. George Stanford University Department of Chemistry Stanford, CA 94305
Dr. A. Reisman Naval Weapons Center of North Carolina Research Triangle Park, North Carolina 27709	Dr. Mark Johnson Yale University Department of Chemistry New Haven, CT 06511-8118
Dr. M. Grunze Surface Science Laboratory University of Maine Orono, Maine 04469	Dr. W. Rieger Hughes Research Laboratory 3011 Malibu Canyon Road Malibu, California 90265
Dr. J. Butler Naval Research Laboratory Code 6115 Washington D.C. 20375-5000	Dr. Theodore E. Hady Surface Chemistry Section Department of Commerce National Bureau of Standards Washington, D.C. 20234
Dr. L. Ingalls Chemistry Department Bentley Analytic Institute Troy, New York 12181	Dr. J. E. Demuth VNA Corporation VNA Research Center P.O. Box 218 Yorktown Heights, New York 12598
Dr. Irvin Ward Chemistry and Physics Department Lincoln University Lincoln University, Pennsylvania 19352	Dr. W. S. Legally Department of Geological and Mining Engineering University of Wisconsin Madison, Wisconsin 53706
Dr. E. J. Glabunde Department of Chemistry Kansas State University Manhattan, Kansas 66506	Dr. R. E. Van Dine Chemistry Department Northern Illinois University DeKalb, Illinois 60137
Dr. C. B. Morris Department of Chemistry University of California Berkeley, California 94720	Dr. J. M. Jolly Department of Chemistry University of Texas Austin, Texas 78712

Q/1113/86/2

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	No. Copies		No. Copies
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code L52 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 92132	1

ABSTRACTS DISTRIBUTION LIST, 055/625/679

Dr. Maria Mehu
Chemistry Department
University of California
Santa Barbara, California 93106

Dr. M. Goddard
Department of Chemistry and Chemical
Engineering
California Institute of Technology
Pasadena, California 91125

Dr. Stephen D. Kavan
Physics Department
University Of Oregon
Eugene, Oregon 97403

Dr. David M. Walba
Department of Chemistry
University of Colorado
Boulder, CO 80309-0215

Dr. A. Stechl
Department of Electrical and
Systems Engineering
Rensselaer Polytechnic Institute
Troy, New York 12181

Dr. S. M. Harrison
Department of Chemistry
Cornell University
Ithaca, New York 14853

Dr. R. Bruce King
Department of Chemistry
University of Georgia
Athens, Georgia 30602

Dr. Richard J. Savally
Department of Chemistry
University of California
Berkeley, California 94720

Dr. Karl Fries, Jr.
SRI International
333 Ravenswood Avenue
Menlo Park, California 94025

Dr. Aaron Fletcher
Code 3852
Naval Weapons Center
China Lake, California 93555

Dr. A. Vold
Department of Chemistry
Brown University
Providence, Rhode Island 02912

Dr. J. Cooper
Code 6170
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. M. C. Baird
Department of Chemistry
Queen's University
Kingston, Canada
K7L 3N6

Dr. R. M. Lichten
Department of Chemistry
Boston University
685 Commonwealth Avenue
Boston, Massachusetts 02215

Dr. R. Eisenberg
Department of Chemistry
University of Rochester
Rochester, New York 14627

Dr. Alan R. Cutler
Department of Chemistry
Rensselaer Polytechnic Institute
Troy, NY 12180-3590

Dr. L. Yasha
Department of Chemistry
Clermont College
Potsdam, New York 13676

Dr. R. A. Huggins
Materials Science and
Engineering Department
Stanford University
Stanford, California 94305

Dr. Carlo Floriani
Mineralogisch-Geologisches
Institut
Place du Croate 3
Lausanne, Switzerland

Dr. Miller Youngs
Department of Chemistry
Case Western Reserve University
Cleveland, OH 44106

Dr. S. John Cooper
Department of Chemistry
University of Pittsburgh
Pittsburgh, PA 15260

Dr. S. D. Worley
Department of Chemistry
Auburn University
Auburn, Alabama 36830

Dr. Thomas J. Peyer
Department of Chemistry
University of North Carolina
Chapel Hill, NC 27516

Dr. Jeffrey Zink
Department of Chemistry
University of California
Los Angeles, California 90024

ABSTRACTS DISTRIBUTION LIST, 056/625/679

Dr. G. A. Somorjai
Department of Chemistry
University of California
Berkeley, California 94720

Dr. J. Purdy
Naval Research Laboratory
Code 6170
Washington, D.C. 20375-5000

Dr. M. T. Perle
Electrical Engineering Department
University of Minnesota
Minneapolis, Minnesota 55455

Dr. Keith M. Johnson
Department of Metallurgy and
Materials Science
Massachusetts Institute of Technology
Cambridge, Massachusetts 02139

Dr. S. Sibener
Department of Chemistry
Jones-France Institute
5840 Ellis Avenue
Chicago, Illinois 60637

Dr. David Green
Quantum Surface Dynamics Branch
Code 3817
Naval Weapons Center
China Lake, California 93555

Dr. A. Vold
Department of Chemistry
Brown University
Providence, Rhode Island 02912

Dr. S. L. Bernasek
Department of Chemistry
Rensselaer Polytechnic
Institute
Troy, New York 12180

Dr. G. King
Department of Physics
University of California, San Diego
La Jolla, California 92037

Dr. L. Kesmodel
Department of Physics
Indiana University
Bloomington, Indiana 47403

Dr. K. C. Janda
University of Pittsburgh
Chemistry Building
Pittsburgh, PA 15260

Dr. E. A. Irene
Department of Chemistry
University of North Carolina
Chapel Hill, North Carolina 27516

Dr. Adam Heller
Bell Laboratories
Murray Hill, New Jersey 07974

Dr. Martin Fleischmann
Department of Chemistry
University of Southampton
Southampton SO9 5NH
UNITED KINGDOM

Dr. M. Tachibana
Chemistry Department
Jackson State University
Jackson, Mississippi 39217

Dr. John M. Wilgus
Cornell University
Laboratory of Atomic and
Solid State Physics
Ithaca, New York 14853

Dr. Ronald Lee
9130
Naval Surface Weapons Center
White Oak
Silver Spring, Maryland 20910

Dr. Robert Evans
Department of Chemistry
University of California
1142 Evans Hall
Berkeley, California 94720

Dr. F. Carter
Code 6170
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. Richard Colton
Code 6170
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. Dan Pierce
National Bureau of Standards
Optical Physics Division
Washington, D.C. 20234

Dr. R. G. Mallis
Department of Physics
University of California
Irvine, California 92696

Dr. G. Ramaker
Chemistry Department
George Washington University
Washington, D.C. 20052

Dr. J. C. Hemminger
Chemistry Department
University of California
Irvine, California 92717

Dr. T. F. George
Chemistry Department
University of Rochester
Rochester, New York 14627

Dr. G. Rubloff
134
Thomas J. Watson Research Center
P.O. Box 217
Yorktown Heights, New York 10598

Dr. J. Feldmann
Department of Chemistry and
Materials Engineering
California Institute of Technology
Pasadena, California 91125

Dr. John J. Stucky
Chemistry Department
University of California
Santa Barbara, CA 93106

Dr. John T. Yates
Department of Chemistry
University of Pittsburgh
Pittsburgh, Pennsylvania 15260

Dr. R. Stanley Williams
Department of Chemistry
University of California
Los Angeles, California 90024

Dr. R. P. Messner
Materials Characterization Lab.
General Electric Company
Schenectady, New York 12307

Dr. J. T. Koster
Department of Chemistry
University of Richmond
Richmond, Virginia 23173

Dr. R. M. Plummer
Department of Physics
University of Pennsylvania
Philadelphia, Pennsylvania 19106

Dr. E. Tager
Department of Chemistry
Case Western Reserve University
Cleveland, Ohio 44106

Dr. R. Minoori
Department of Chemistry
Pennsylvania State University
University Park, Pennsylvania 16802

Dr. David Hoffman
Department of Chemistry
Cornell University
Ithaca, New York 14853

Dr. Robert L. Houston
Department of Chemistry
University of California
Los Angeles, CA 90024

Dr. Robert M. Waymouth
Department of Chemistry
University of California
Berkeley, CA 94720

END
FILMED
FEB. 1988
DTIC