

SECURITY CLASSIFICATION OF THIS PAGE

REPORT DOCUMENTATION PAGE

AD-A198 500		TIC ECTE JUL 1 1 1988 D		1d. RESTRICTIVE MARKINGS													
2b. DECLASSIFICATION/CONTROLS				3. DISTRIBUTION/AVAILABILITY OF REPORT Approved for public release; distribution unlimited.													
4. PERFORMING ORGANIZATION REPORT NUMBER(S)		AFOSR-TR-88-0578		5. MONITORING ORGANIZATION REPORT NUMBER(S)													
6a. NAME OF PERFORMING ORGANIZATION Georgia Inst of Tech Rsch		6b. OFFICE SYMBOL (If applicable)		7a. NAME OF MONITORING ORGANIZATION AFOSR/NE													
6c. ADDRESS (City, State and ZIP Code) Alanta, Georgia 30332				7b. ADDRESS (City, State and ZIP Code) Bldg 410 Bolling AFB, DC 20332-6448													
8a. NAME OF FUNDING/SPONSORING ORGANIZATION AFOSR/NE		8b. OFFICE SYMBOL (If applicable)		9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER AFOSR 87-0162													
8c. ADDRESS (City, State and ZIP Code) Bldg 410 Bolling AFB, DC 20332-6448				10. SOURCE OF FUNDING NOS. <table border="1"><tr><td>PROGRAM ELEMENT NO.</td><td>PROJECT NO.</td><td>TASK NO.</td><td>WORK UNIT NO.</td></tr><tr><td>61102F</td><td>2306</td><td>A1</td><td></td></tr></table>		PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT NO.	61102F	2306	A1					
PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT NO.														
61102F	2306	A1															
11. TITLE (Include Security Classification) Cyclic Deformation, Damage, and Effects of Environment in the Ni ₃ Al Ordered Alloy at Elevated Temperatures																	
12. PERSONAL AUTHOR(S) Dr. Antolovich																	
13a. TYPE OF REPORT Annual		13b. TIME COVERED FROM 01 May 87 to 01 May 88		14. DATE OF REPORT (Yr., Mo., Day)													
				15. PAGE COUNT													
16. SUPPLEMENTARY NOTATION																	
17. COSATI CODES <table border="1"><tr><td>FIELD</td><td>GROUP</td><td>SUB. GR.</td></tr><tr><td></td><td></td><td></td></tr><tr><td></td><td></td><td></td></tr><tr><td></td><td></td><td></td></tr></table>		FIELD	GROUP	SUB. GR.										18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)			
FIELD	GROUP	SUB. GR.															
19. ABSTRACT (Continue on reverse if necessary and identify by block number) A basic program is defined to investigate cyclic deformation, damage accumulation, and fatigue crack propagation (FCP) in the ordered Ni₃Al system as affected by composition, temperature, and environment. While this class of ordered alloys shows great promise for elevated temperature applications in jet and rocket engines, problems of brittleness and damage by hostile environments have been encountered in monotonic tensile deformation. The basic mechanisms of cyclic deformation and fatigue crack propagation have not been fully investigated; yet must be understood if these materials are to be used in advanced applications. <i>Nickel Alloy</i>																	
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT UNCLASSIFIED/UNLIMITED ☐ SAME AS RPT. ☐ DTIC USERS ☐		21. ABSTRACT SECURITY CLASSIFICATION UNCLASSIFIED															
22a. NAME OF RESPONSIBLE INDIVIDUAL ROSENSTEIN		22b. TELEPHONE NUMBER (Include Area Code) (202) 767-4933		22c. OFFICE SYMBOL NE													

AFOSR-TR. 88-0578

CYCLIC DEFORMATION, DAMAGE, AND EFFECTS OF ENVIRONMENT
IN THE Ni_3Al ORDERED ALLOY AT ELEVATED TEMPERATURES



PREPARED BY:

Stephen D. Antolovich

Professor and Director
School of Materials Engineering
Georgia Institute of Technology
Atlanta, Georgia 30332

Accession For	
NTIS CRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

Progress Report for period 5-1-87 through 5-1-88
Contract No. AFOSR-87-0162

Air Force Office of Scientific Research
Electronic and Material Sciences
Building 410
Bolling AFB, D.C. 20332

Program Manager: Dr. A. H. Rosenstein

88 6 30 010

I. Program Overview

In this study, a basic program is defined to investigate cyclic deformation, damage accumulation, and fatigue crack propagation (FCP) in the ordered Ni_3Al system as affected by composition, temperature, and environment. While this class of ordered alloys shows great promise for elevated temperature applications in jet and rocket engines, problems of brittleness and damage by hostile environments have been encountered in monotonic tensile deformation. The basic mechanisms of cyclic deformation and fatigue crack propagation have not been fully investigated; yet they must be understood if these materials are to be used in advanced applications.

II. Program Status

A. Material Preparation

To investigate the role of boron in improving the ductility of this class of material two compositions were chosen, one which exhibits brittle behavior and the other which exhibits non-brittle behavior. Two other compositions, one subject to environmental influences and the other possessing relative insensitivity to environment will be used will be used to study the mechanisms of environmental embrittlement under conditions of cyclic loading.

Powder metallurgy techniques were used for the production of the above mentioned alloys by Homogeneous Metals, Inc. Each of the four alloys was produced by atomization of the melt resulting

in power particles having identical chemistries. The powder alloys were then screened to +80-400 and extruded to produce 12' long bars approximately 2" in diameter which yielded nearly 200 lbs. of usable material of each of the four compositions. In addition, 50 lbs. of excess powder material for each of the four alloys was obtained which can be used in future investigations.

The compositions of the alloys are as follows;


Alloy	Ni	Al	Atomic Percent				S	N ₂ (ppm)	O ₂ (ppm)
			Cr	B	C				
A	Bal	12.91	0.0	.045	.0099	<.001	4	170	
B	Bal	12.41	0.0	.048	.0066	<.001	5	72	
C	Bal	10.26	8.0	.046	.0075	<.001	3	84	
D	Bal	8.70	7.7	.046	.0060	<.001	3	84	

In addition to the +80-400 powder, a small section attach to the end of each extrusion consisting of -400 mesh powder was produced providing an opportunity to fabricate a limited number of samples from very fine powder material.


Optical metallagraphy of the extruded material reveals a fine grain material, ~80 μ m, in both the transverse and longitudinal directions as shown in Fig. 1. Orientation studies utilizing the transmission electron microscope are currently underway to determine if any crystallographic texturing occurred as the result of the extrusion process. The grains consist of both a dendritic and a lamellar structure with different lamellar spacings present within a given alloy.

Because Ni_3Al can exist over a range of compositions it is possible that the microstructure consists of a partially ordered solid solution whose composition varies in a systematic fashion. It is also possible that two phases are present, one being the strongly ordered Ni_3Al and the other a random solid solution of nickel. X-ray diffractometry studies of the alloys are underway to establish the degree of order in each alloy by measuring the intensity of the superlattice reflections. A typical structure as seen in the TEM is shown in Fig. 2.

Low cycle fatigue, Tensile, and FCP specimens will be machined from the extruded rods. Machining is to be performed by Mastersons Manufacturing and is expected to be completed by June 1988.

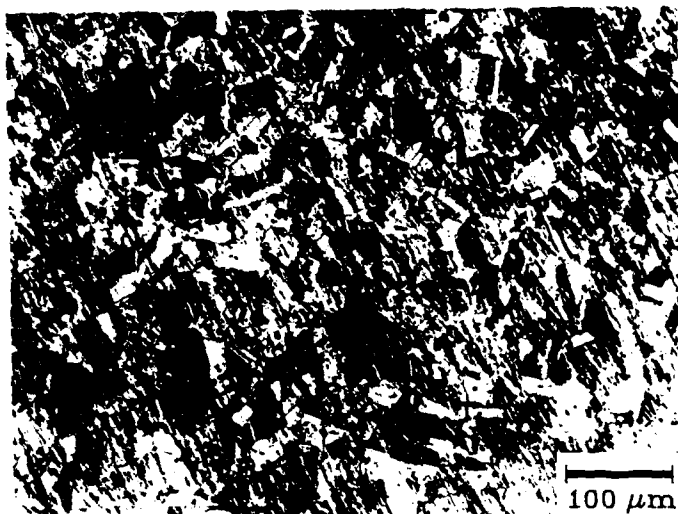

(a)

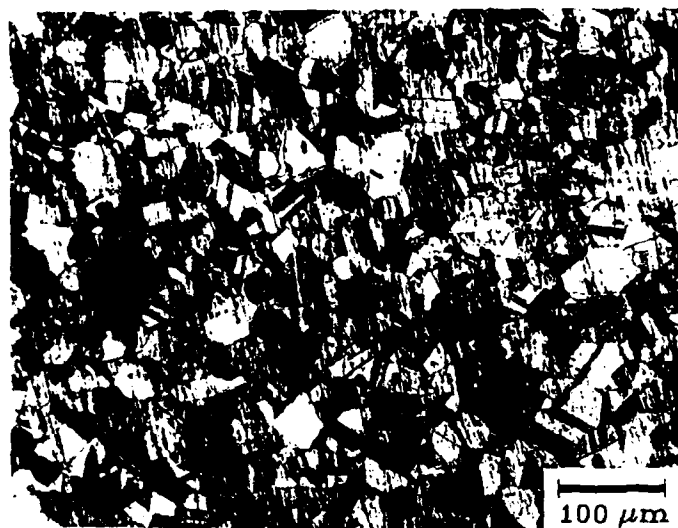

(b)

Figure 1 - Optical micrograph of specimen C, -80/+400 mesh
along a) longitudinal and b) transverse direction.



Figure 2 - TEM micrograph of specimen C, -400 mesh showing low dislocation density and small grain size due to rapid cooling during atomization.

END
DATE
FILMED

DTIC
10-88