

AD-A207 719

DTIC FILE COPY

4

A Study of the T(1) Transition of
Poly[bis(trifluoroethoxy)phosphazene]
(PBFP) Using Solid-State Nuclear
Magnetic Resonance Spectroscopy

by

Scott G. Young and Joseph H. Magill

MATERIALS SCIENCE AND ENGINEERING

University of Pittsburgh

Pittsburgh, Pennsylvania 15261



DTIC
ELECTE
MAY 12 1989
S E D

This document has been approved
for public release and makes its
distribution is unlimited.

89 5 12 008

**A Study of the T(1) Transition of
Poly[bis(trifluoroethoxy)phosphazene]
(PBFP) Using Solid-State Nuclear
Magnetic Resonance Spectroscopy**

by

Scott G. Young and Joseph H. Magill

**School of Engineering
University of Pittsburgh
Pittsburgh, PA 15261**

DTIC
ELECTE
MAY 12 1989
S E D

This document has been approved
for public release and under its
distribution is unlimited.

ADA207719

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION None			1b. RESTRICTIVE MARKINGS None		
2a. SECURITY CLASSIFICATION AUTHORITY None			3. DISTRIBUTION/AVAILABILITY OF REPORT Unlimited		
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE None					
4. PERFORMING ORGANIZATION REPORT NUMBER(S) ONR # 11			5. MONITORING ORGANIZATION REPORT NUMBER(S) ONR N00014-85-K-0358		
6a. NAME OF PERFORMING ORGANIZATION University of Pittsburgh		6b. OFFICE SYMBOL (If applicable)		7a. NAME OF MONITORING ORGANIZATION Office of Naval Research	
6c. ADDRESS (City, State, and ZIP Code) 848 Benedum Engineering Hall School of Engineering Univ. of Pittsburgh, Pgh., PA 15261			7b. ADDRESS (City, State, and ZIP Code) 800 North Quincy Avenue Arlington, VA 22217		
8a. NAME OF FUNDING/SPONSORING ORGANIZATION Office of Naval Research		8b. OFFICE SYMBOL (If applicable)		9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER	
8c. ADDRESS (City, State, and ZIP Code) 800 North Quincy Avenue Arlington, VA 22217			10. SOURCE OF FUNDING NUMBERS		
			PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.
11. TITLE (Include Security Classification) A Study of the T(1) Transition of Poly[bis(trifluoroethoxy)phosphazene] Using Solid State NMR Spectroscopy					
12. PERSONAL AUTHOR(S) S. G. Young and J. H. Magill					
13a. TYPE OF REPORT		13b. TIME COVERED FROM 1985 TO		14. DATE OF REPORT (Year, Month, Day) 1989 / 5 / 4	
15. PAGE COUNT 14					
16. SUPPLEMENTARY NOTATION To be published in "Macromolecules" in 1989.					
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)		
FIELD	GROUP	SUB-GROUP			
			in equilibrium with		
19. ABSTRACT (Continue on reverse if necessary and identify by block number)					
In situ solid state variable temperature NMR measurements have been made on Poly[bis(trifluoroethoxy)phosphazene] above and below the first order thermotropic transition, T(1). A single mobile ordered 2D phase exists above T(1). Below T(1) and at room temperature there is a 3D phase in agreement with other physical property measurements. The OCH_2CF_3 side chains exhibit similar mobility on either side of the 2D $\rightleftharpoons$ 3D transition. The activation energies associated with the CH_2 and CF_3 side groups are $E_{\text{CH}_2} = 17.3$ kJ/mole and $E_{\text{CF}_3} = 13.7$ kJ/mole. The spin lattice relaxation measurements for these same groups are 1.75s. and 3.55s. respectively. The crystallinity ascertained from solid state NMR results is strongly dependent upon annealing conditions and temperature of measurement. Sub CF3 Key words: Solid State NMR; polyphosphazene; conformational mobility, activation energies and relaxation times. Nuclear Magnetic Resonance. phosphazene. 11d1k Sub CF2 about =					
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT ☐ UNCLASSIFIED/UNLIMITED ☒ SAME AS RPT. ☐ DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION		
22a. NAME OF RESPONSIBLE INDIVIDUAL Dr. Kenneth J. Wynne			22b. TELEPHONE (Include Area Code) 202-696-4409		22c. OFFICE SYMBOL

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>	
Office of Naval Research Attn: Code 413 800 N. Quincy Street Arlington, Virginia 22217	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529
Dr. Bernard Doude Naval Weapons Support Center Code 5042 Crane, Indiana 47522	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Washington, D.C. 20360	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112
OTNSRDC Attn: Dr. G. Bosmajian Applied Chemistry Division Annapolis, Maryland 21401	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375	1	

Accession For	
NTIS GRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	



**A STUDY OF THE T(1) TRANSITION OF
POLY[BIS(TRIFLUOROETHOXY)PHOSPHAZENE] (PBFP) USING
SOLID-STATE NUCLEAR MAGNETIC RESONANCE SPECTROSCOPY**

Scott G. Young and Joseph H. Magill*

School of Engineering
University of Pittsburgh
Pittsburgh, PA 15261

Background

Considerable interest has been developed in thermotropic polymers generally over the past decade or more.¹⁻³ In semicrystalline polyphosphazenes three transitions have been established: glass temperature T_g , thermotropic (mesophase) transition $T(1)$, and melting transition, T_m . Whenever the side group chemistry is altered these parameters scale linearly⁴ in a plot of $(T_m - T_g)/(T_m - T(1))$ against $T(1)/T_m$. The first order transitions $T(1)$ and T_m are well known for PBFP,³ typically $T(1) \sim 85^\circ\text{C}$ and $T_m \sim 242^\circ\text{C}$. T_g lies well below these transitions at -66°C approximately. Interestingly, there is a significant change in the location and magnitude of the $T(1)$ transition whenever polyphosphazenes are heated and cooled. In PBFP specifically crystallized from solution, samples are usually spherulitic. Small angle X-ray measurements made on crystal mats formed at room temperature, indicate that lamellae of $\sim 140 \text{ \AA}$ are obtained. The crystallinity of these specimens is surprisingly low ($< 50\%$) and the crystal structure is monoclinic. When heated through $T(1)$ the sample undergoes some form of chain extension. The thermotropic state is comprised of molecules hexagonally packed in arrays or domains. In this condition they have considerable fluidity as creep and other measurements substantiate.⁵ The interchain spacing has been assessed by X-ray and electron

*also Materials Science and Engineering Department

diffraction⁶ which confirms the hexagonal arrangement in the 2D δ -state.^{6,7} Whenever PBFP is cooled from the molten state it returns very rapidly to the 2D hexagonally packed phase and finally crystallizes into a 3D orthorhombic structure below $T(1)^{**}$ (i.e., different from the original monoclinic form). Apparently the transformation occurs through relatively small displacements or translations in the chain direction so as to allow growth to occur laterally with an Avrami⁸ $n=2$. The crystallinity of PBFP returned to room temperature is much higher than the starting specimen and the location and enthalpy of the $T(1)$ transition is increased substantially upon thermal cycling. The chain packing and the resultant 3D ordering shows that $T(1)$ and $\Delta H[T(1)]$ asymptotically approach an upper limit in PBFP and in other polyphosphazenes.³ Dilatometry measurements⁵ clearly indicates the first order nature of $T(1)$ and T_m as well as a significant volume change ($\sim 6\%$) that is associated with material expansion and enhanced mobility that occurs at both of these temperatures.

Wide-line nuclear magnetic resonance (NMR) and X-ray measurements were made on PBFP about a decade ago.⁹ It was reported that the thermotropic state of this polymer is involved with rapidly rotating chains in a hexagonal lattice that exhibited both lateral order and longitudinal disorder. This condition or state was attributed to the onset of rapid side group and backbone chain motions.

Now that solid-state NMR has emerged as a technique for studying local molecular dynamics and conformational changes through decoupling side group and main chain motions, its application to polyphosphazenes is not surprising. The first high-resolution solid-state NMR study of polyphosphazenes was reported only one year ago by Crosby and Haw.¹⁰ ^{31}P magic-angle spinning (MAS) NMR was used to examine the hydrolysis and cross-linking of poly(dichlorophosphazene). The molecular dynamics of poly(dimethoxyphosphazene) (PBMP) and poly(diethoxyphosphazene) (PBEP) was studied using ^{31}P MAS and ^{13}C cross-polarization (CP)/MAS NMR at various temperatures. The results from this investigation indicate that the main chains of PBEP and PBMP are undergoing large-amplitude anisotropic motions above their respective glass transition temperatures. Crosby and Haw concluded that ^{31}P MAS and ^{13}C

^{**}After the first thermal cycle through $T(1)$, the 3D orthorhombic phase dominates below $T(1)$.

CP/MAS NMR can be used to study molecular dynamics in phosphazene polymers.

More recently Tonelli and coworkers^{11, 12} investigated the phase transitions of poly[bis(p-ethylphenoxy)phosphazene] (PBEPP). They used ^{31}P MAS/dipolar decoupling (DD) at several temperatures and found a sudden decrease in line width corresponding to the crystal - liquid crystal transition which occurred above 100°C. They concluded that considerable backbone motion occurs whenever PBEPP passes into the thermotropic phase. From the spin-lattice relaxation times, T_1 , of the carbon atoms on the side group, they reported that the side chains were also mobile in the thermotropic phase. According to this work, short spin-lattice relaxation times observed only for the protonated aromatic carbons in the 3D crystal indicate that phenyl rings are mobile and rotating about their 1,4-axes even below the T(1) transition.

Experimental

Solution crystallized poly[bis(trifluoroethoxy)phosphazene], PBFP ($M_w = 300,000$ and $M_w/M_n = 2.3$), was studied in our laboratory using ^{31}P and ^{13}C MAS variable temperature NMR. ^1H decoupling was used for ^{13}C but not for ^{31}P . The spectra were recorded between room temperature and 100°C on a Bruker MSL 300 NMR spectrometer. Magic angle sample spinning was performed at speeds of 2.0 - 4.0 kHz. The samples were spun in aluminum oxide rotors with teflon end caps. ^{31}P spectra were recorded at 10°C intervals from 20°C to 100°C which was the upper limit of this equipment. The sample was then cooled at 10° intervals and spectra were recorded at each interval. This procedure was repeated to ensure reproducibility.

Figure 1a shows selected ^{31}P NMR spectra for PBFP obtained during the heating process at 20°C, 60°C, and 100°C and Figure 1b provides spectra recorded during the cooling process at 80°C, 50°C, and 20°C. Below the T(1) transition there are two peaks corresponding to the amorphous^{***} and crystalline regions respectively. As the polymer is heated through T(1) and cooled down again to room temperature the peak area corresponding to the crystalline region increases, in accordance with DSC and X-ray measurements. The relative areas of the crystalline and amorphous peaks are listed in

^{***}Amorphous in this context is presumed to be structure that is less than 3D order.

Table 1 as a function of thermal history.

The ^{31}P chemical shift referenced against H_3PO_4 (0 ppm) of the amorphous phase decreases as the temperature increases. A small increase in the ^{31}P chemical shift occurs just before the T(1) transition temperature is reached corresponding to a change in conformation as the chain backbone extends. This change is affected by the coexisting crystalline phase. The decrease in magnitude of the chemical shift suggests that the nuclei are becoming more shielded as the temperature is increased during the transformation into the 2D thermotropic phase. The magnitude of the chemical shift increases with thermal cycling as the state of the material alters.

The temperature dependence of the ^{31}P line width of the amorphous phase during the first heating cycle is shown in Figure 2. Note that the line width sharpens as more thermal energy enters the sample, except at temperatures just before the T(1) transition. The increase in the line width which occurs just before T(1) is reached is probably due to reorganization taking place before this transition. Cooling after the heating cycle results in an increase in the spectral line width that is measured at room temperature. During the second heating the spectral line width drops to a minimum value before peaking at approximately 75°C , as compared to 50°C that is observed for the first heating cycle. An enhancement of 3D ordering occurs upon cycling the sample as the results in Table 1 indicate.

^{13}C MAS ^1H decoupled NMR spectra of PBFP obtained at 23°C and 100°C were almost identical except for a small decrease in line width of the single peak which is consistent with the enhanced mobility of the CH_2 portion of the side group in $[-\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2-]_x$. As the sample passes through the T(1) transition it occupies a larger volume according to dilatometry results made on PBFP.⁵ It therefore follows that the side chains have mobility even in the 3D phase of PBFP. The fluorine atoms on the end carbon atom split the signal into a quartet as anticipated from their chemical structure. Furthermore, ^{13}C spin-lattice relaxation measurements made through T(1) for the CH_2 and CF_3 side groups on PBFP are 1.7 seconds and 3.5 seconds respectively. The corresponding activation energies associated with these groups are estimated to be $E_{\text{CH}_2} \sim 17.3 \text{ kJ/mol}$ and $E_{\text{CF}_3} \sim 13.7 \text{ kJ/mol}$.

Since the upper temperature limit for in situ spinning in our Bruker spectrometer was limited to 100°C, the PBFP sample was annealed at 200°C outside of the instrument and slowly cooled to room temperature again. The ^{31}P MAS NMR plot of line width vs. temperature of this sample is shown in Figure 3. The spectral line width measured at room temperature is now much broader than it was before annealing. However, as the specimen temperature is increased stepwise in 10°C intervals to 100°C, the line width sharpens. This behavior is more pronounced (three to four times), but it is still consistent with the trend found before annealing. The increased line width observed at 30°C is due to the inherently higher crystallinity, which now suppresses the mobility of the phosphorus-nitrogen backbone below $T(1)$. These results are in accord with the observations of Sun and Magill³ who found that annealing and thermal cycling of PBFP and other polyphosphazenes also increases their crystallinity. Solution ^{31}P NMR was performed on the PBFP sample to determine if the chemical structure was altered due to annealing. A sharp singlet at -6.9 ppm before and after annealing indicated that no chemical change had occurred.

In conclusion, these preliminary results serves to show that solid-state variable temperature NMR is a useful technique that can be used to study in situ molecular chain dynamics, chain conformation, and specimen crystallinity, in accordance with the morphology of PBFP. Two distinct crystalline and amorphous regions are clearly exhibited by the chain backbone below $T(1)$. A single highly mobile ordered 2D phase exists above $T(1)$ in line with our other solid state observations and properties. The $-\text{OCH}_2\text{CF}_3$ side branches of the polymer exhibit mobility below the $T(1)$ transition and appear to have a similar mobility and conformation on either side of the $T(1)$ transition. The crystalline-amorphous ratio in PBFP assessed by solid-state NMR is strongly dependent upon annealing conditions and temperature of measurement.

Acknowledgments

The authors thank Professor George Marcelin for use of the NMR facilities. Dr. F. T. Lin for performing the solution NMR, the National Science Foundation (Polymers Program), and the Office of Naval Research (Chemistry Division) for support of the work.

References

1. Singler, R. E., Schneider, N. S., and Hagnauer, G. L., *Polymer Eng. Sci.*, **1975**, 15, 321.
2. Allcock, H. R., *Sci. Prog.*, **1980**, 66, 355.
3. Sun, D. C. and Magill, J. H., *Polymer*, **1987**, 28, 1243.
4. Kojima, M. and Magill, J. H. in "*Morphology of Polymers*", B. Sedlacek, ed., Walter de Gruyter & Co., New York, 1986.
5. Masuko, M., Simeone, R. L., Magill, J. H., and Plazek, D. J., *Macromolecules*, **1984**, 17, 2857.
6. Kojima, M. and Magill, J. H., *Die. Makromol. Chemie*, **1985**, 186, 649.
7. Schneider, N. S. and Desper, C. R. in "*Liquid Crystalline Order*", A. Blumstein, ed., Chap. 9, Academic Press, New York, 1978.
8. Ciora, R. J., Sun, D. C., and Magill, J. H., *Proceedings Sixteenth North American Thermal Analysis Society*, Washington, D. C., Sept. 27-30 1987, p. 325.
9. Alexander, M. N., Desper, C. R., Sagalyn, P. L., and Schneider, N. S., *Macromolecules*, **1977**, 10, 721.
10. Crosby, R. C. and Haw, J. F., *Macromolecules*, **1987**, 20, 2324.
11. Tonelli, A. E., Gomez, M. A., Tanaka, H., and Schilling, F. C., *Polymer Preprints*, **1988**, 29, 440.
12. Tanaka, H., Gomez, M. A., Tonelli, A. E., Chichester-Hicks, S. V., and Haddon, R. C., *Macromolecules*, **1988**, 21, 2301.

LIST OF FIGURES

- Figure 1a ^{31}P NMR spectra of PBFP at 20°C, 60°C, and 100°C during heating.
- Figure 1b ^{31}P NMR spectra of PBFP at 80°C, 50°C, and 20°C during cooling from 100°C.
- Figure 2 ^{31}P MAS line width from the amorphous phase of PBFP during heating and cooling (first thermal cycle).
- Figure 3 ^{31}P MAS line width of PBFP during heating and cooling after annealing at 200°C.

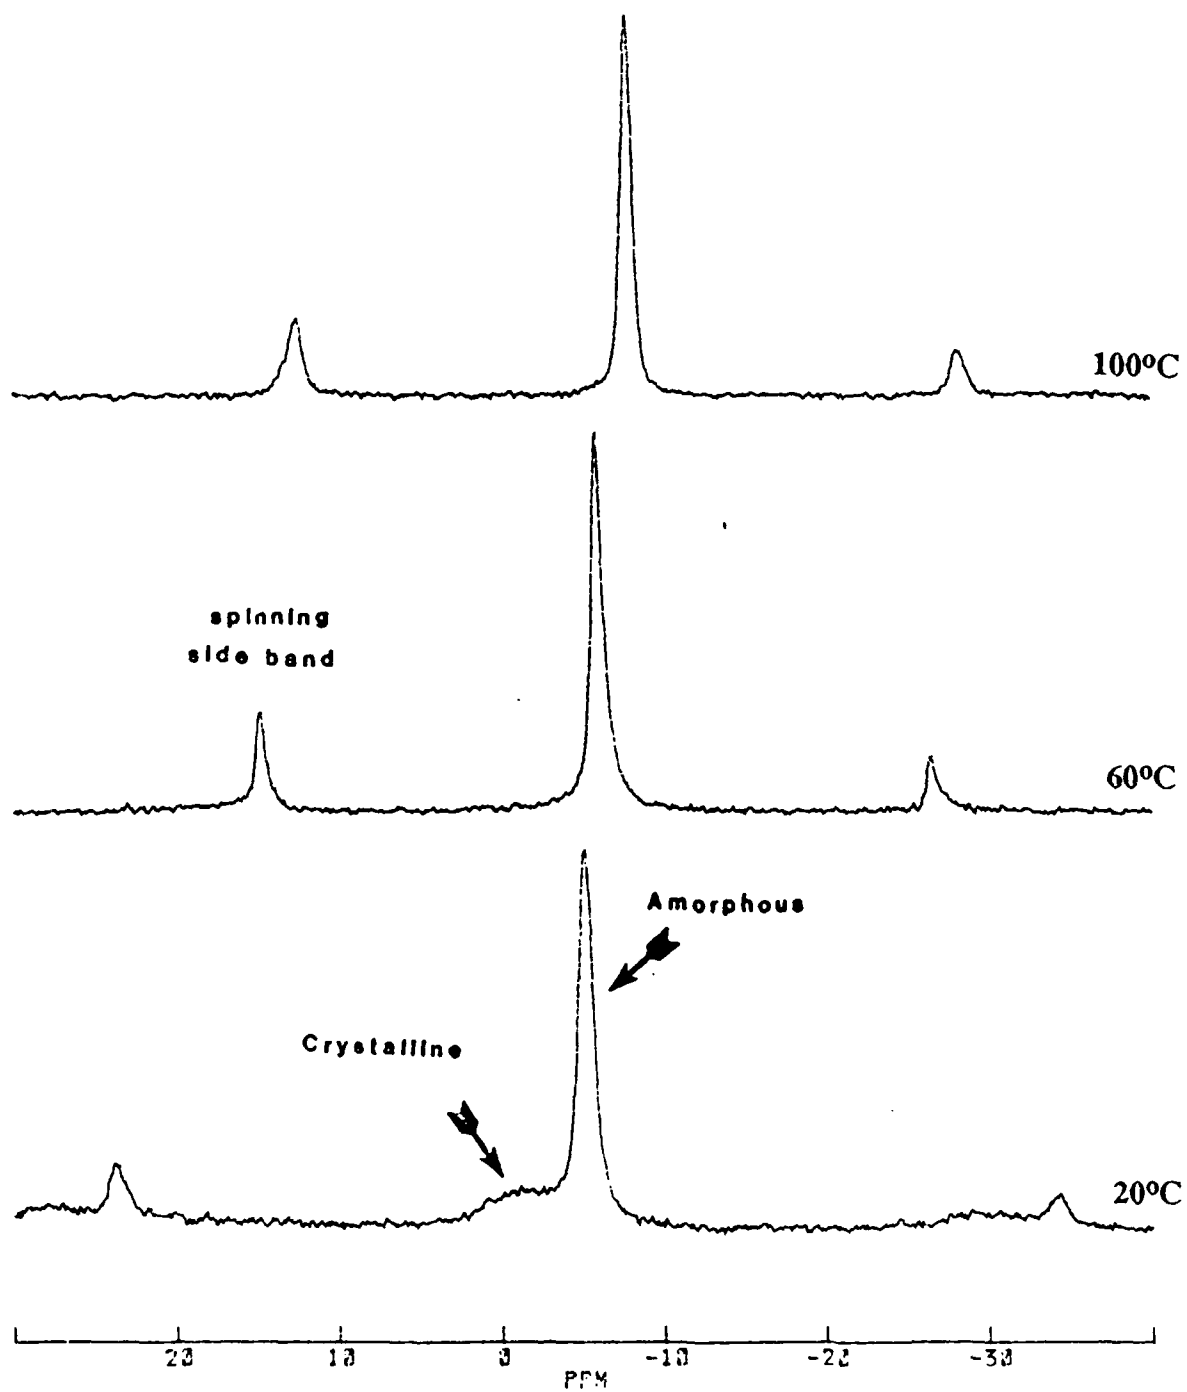


Figure 1a

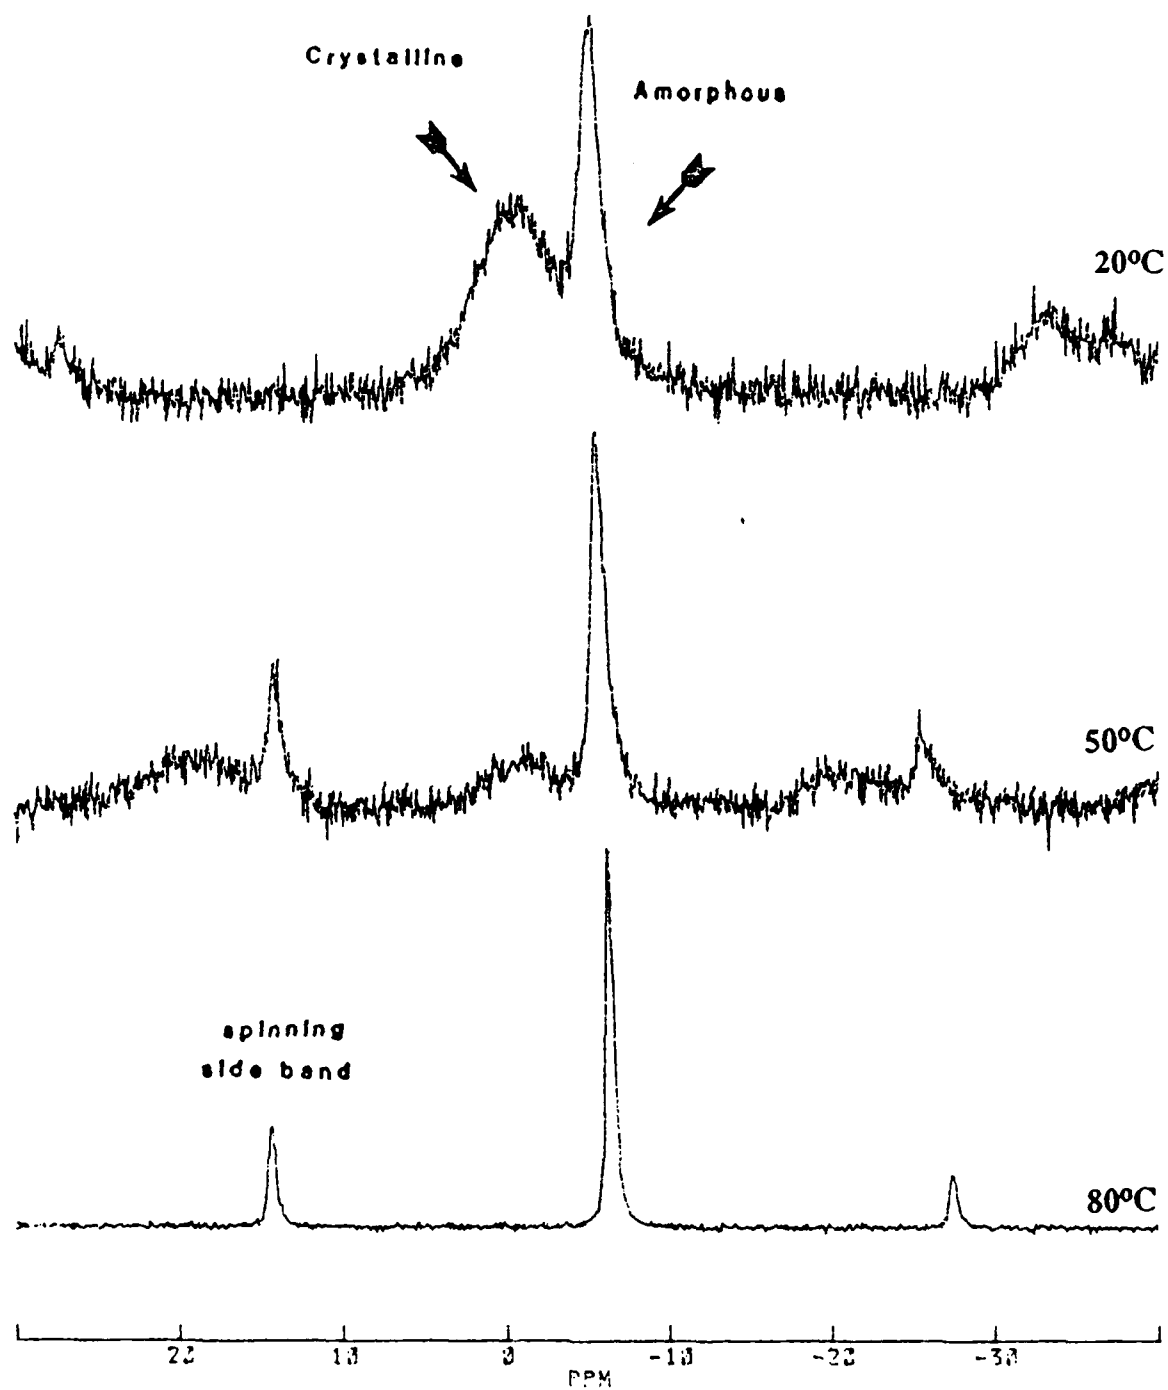


Figure 1b

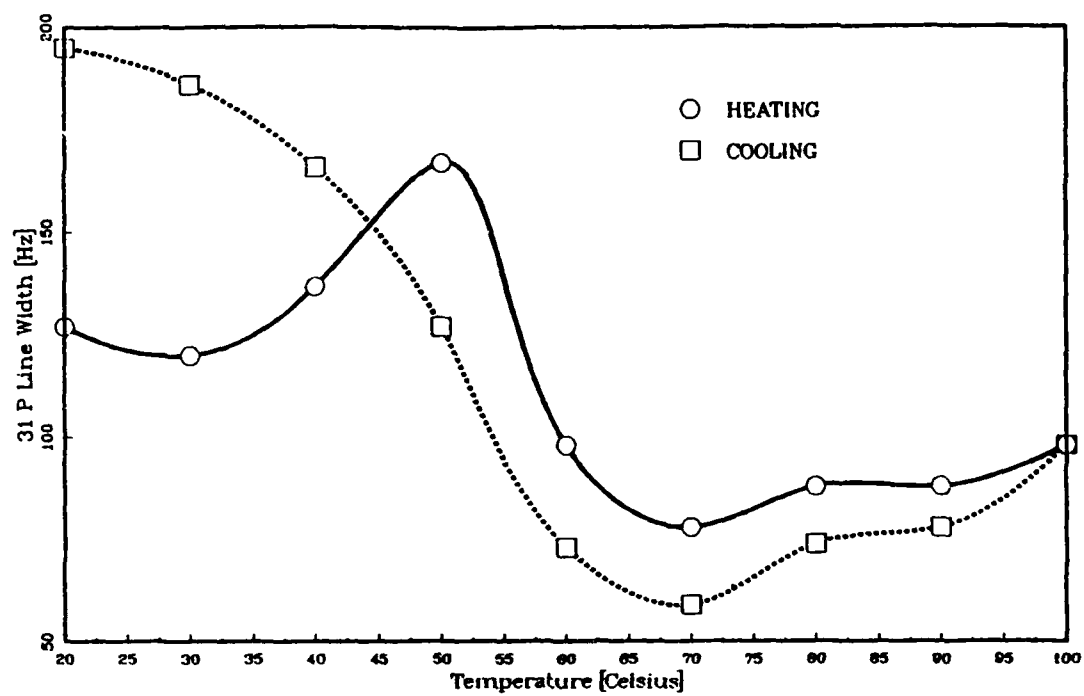


Figure 2

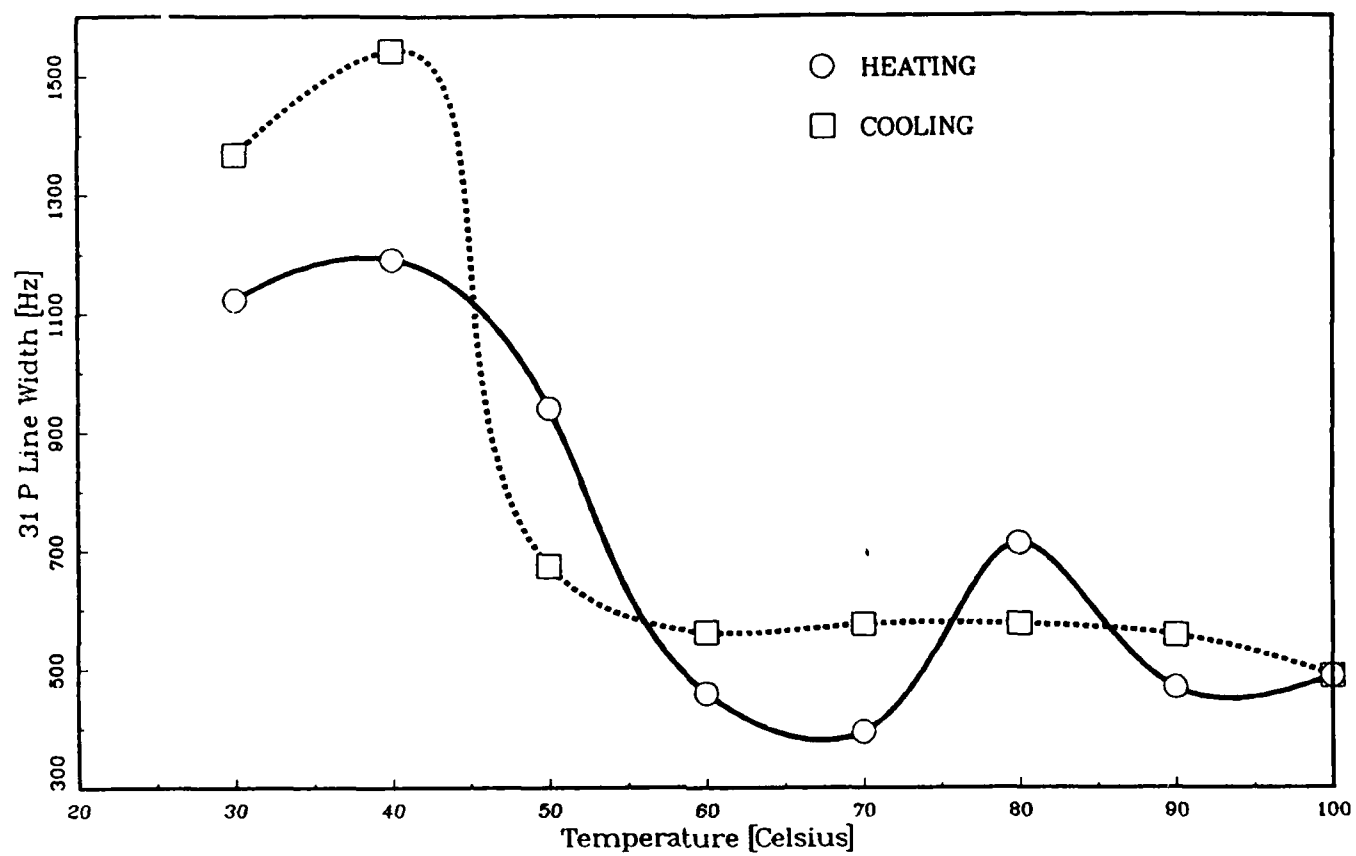


Figure 3

LIST OF TABLES

Table 1	Percent crystallinity of PBFP assessed from relative areas of the amorphous and crystalline ^{31}P peaks.
----------------	--

Table 1

Temperature (°C)	Crystallinity	Amorphous
1 st Heating		
20	25%	75%
30	25%	75%
40	16%	84%
50	9%	91%
1 st Cooling		
50	35%	65%
40	48%	52%
30	50%	50%
20	54%	46%
2 nd Heating		
30	52%	48%
40	41%	59%
50	14%	86%
2 nd Cooling		
60	23%	77%
40	35%	65%
24	54%	46%