

2

FILE COPY

AD-A208 607

OFFICE OF NAVAL RESEARCH  
CONTRACT N00014-82-K-0322  
Task No. NR P00 007

TECHNICAL REPORT NO. 27

STOICHIOMETRIC AND CATALYTIC RING OPENING OF  
HEXAALKYLCYCLODISILAZANES BY ORGANOALKALI REAGENTS

by

Dietmar Seyferth, Joanne M. Schwark and Regina M. Stewart

DTIC  
ELECTE  
MAY 19 1989  
S D

To be published in

"Organometallics"

Department of Chemistry  
Massachusetts Institute of Technology  
Cambridge, MA 02139

May 13, 1989

Reproduction in whole or in part is permitted for any purpose of the  
United States Government

This document has been approved for public release and sale; its distribution  
is unlimited

89 013

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

## REPORT DOCUMENTATION PAGE

|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                              |       |                                      |                                                                                                     |                                                    |
|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------|--------------------------------------|-----------------------------------------------------------------------------------------------------|----------------------------------------------------|
| 1a. REPORT SECURITY CLASSIFICATION<br>Unclassified                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                           |       |                                      | 1b. RESTRICTIVE MARKINGS                                                                            |                                                    |
| 2a. SECURITY CLASSIFICATION AUTHORITY                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                        |       |                                      | 3. DISTRIBUTION / AVAILABILITY OF REPORT<br>Approved for public release.<br>Distribution unlimited. |                                                    |
| 2b. DECLASSIFICATION / DOWNGRADING SCHEDULE                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                  |       |                                      |                                                                                                     |                                                    |
| 4. PERFORMING ORGANIZATION REPORT NUMBER(S)<br>27                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                            |       |                                      | 5. MONITORING ORGANIZATION REPORT NUMBER(S)                                                         |                                                    |
| 6a. NAME OF PERFORMING ORGANIZATION<br>Massachusetts Institute of Technology                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                 |       | 6b. OFFICE SYMBOL<br>(if applicable) | 7a. NAME OF MONITORING ORGANIZATION<br>ONR                                                          |                                                    |
| 6c. ADDRESS (City, State, and ZIP Code)<br>Department of Chemistry<br>77 Massachusetts Avenue<br>Cambridge, MA 02139                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                         |       |                                      | 7b. ADDRESS (City, State, and ZIP Code)<br>Department of Navy<br>Arlington, VA 22217                |                                                    |
| 8a. NAME OF FUNDING / SPONSORING ORGANIZATION<br>ONR                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                         |       | 8b. OFFICE SYMBOL<br>(if applicable) | 9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER                                                     |                                                    |
| 8c. ADDRESS (City, State, and ZIP Code)<br>Department of Navy<br>Arlington, VA 22217                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                         |       |                                      | 10. SOURCE OF FUNDING NUMBERS                                                                       |                                                    |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                              |       |                                      | PROGRAM ELEMENT NO.<br>N-00014-82                                                                   | TASK NO.<br>P00007                                 |
| 11. TITLE (Include Security Classification)<br>STOICHIOMETRIC AND CATALYTIC RING OPENING OF HEXAALKYLCYCLODISILAZANES BY ORGANOALKALI REAGENTS<br>unclassified                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                               |       |                                      |                                                                                                     |                                                    |
| 12. PERSONAL AUTHOR(S)<br>Dietmar Seyferth, Joanne M. Schwark, and Regina M. Stewart                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                         |       |                                      |                                                                                                     |                                                    |
| 13a. TYPE OF REPORT<br>Preprint                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                              |       | 13b. TIME COVERED<br>FROM TO         |                                                                                                     | 14. DATE OF REPORT (Year, Month, Day)<br>1989-5-13 |
| 15. PAGE COUNT                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                               |       |                                      |                                                                                                     |                                                    |
| 16. SUPPLEMENTARY NOTATION<br>Manuscript "Organometallics"                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                   |       |                                      |                                                                                                     |                                                    |
| 17. COSATI CODES                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                             |       |                                      | 18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)                   |                                                    |
| FIELD                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                        | GROUP | SUB-GROUP                            | preceramic polymers, ceramic materials, polysilazanes, silanes, polysilanes, polymers               |                                                    |
| /                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                            |       |                                      |                                                                                                     |                                                    |
| /                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                            |       |                                      |                                                                                                     |                                                    |
| 19. ABSTRACT (Continue on reverse if necessary and identify by block number)<br>The action of organoalkali reagents (RLi, RLi/Me <sub>3</sub> CONa, RLi/Me <sub>3</sub> COK) on cyclo-(Me <sub>2</sub> SiNMe) <sub>2</sub> and cyclo-(Me <sub>2</sub> SiNPr) <sub>2</sub> results in ring opening to give alkali metal amides of the type RMe <sub>2</sub> SiNMeSiMe <sub>2</sub> NMe <sub>2</sub> (M= Li, Na, K) which react with chlorosilanes, R'Me <sub>2</sub> SiCl, to give the expected linear trisilazanes. Relatively unhindered lithium amides also open the cyclo-(Me <sub>2</sub> SiNMe) <sub>2</sub> ring. The use of a catalytic amount of RLi or RLi/Me <sub>3</sub> CONa (but not of RLi/Me <sub>3</sub> COK) results in ring opening polymerization of cyclo-(Me <sub>2</sub> SiNMe) <sub>2</sub> but not of the more hindered cyclo-(Me <sub>2</sub> SiNPr) <sub>2</sub> . |       |                                      |                                                                                                     |                                                    |
| 20. DISTRIBUTION / AVAILABILITY OF ABSTRACT<br><input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                           |       |                                      | 21. ABSTRACT SECURITY CLASSIFICATION<br>unclassified                                                |                                                    |
| 22a. NAME OF RESPONSIBLE INDIVIDUAL<br>Dr. K.J. Wynne                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                        |       |                                      | 22b. TELEPHONE (Include Area Code)<br>202/696-4410                                                  | 22c. OFFICE SYMBOL                                 |

**STOICHIOMETRIC AND CATALYTIC RING OPENING OF  
HEXAALKYLCYCLODISILAZANES BY ORGANOALKALI REAGENTS.**

Dietmar Seyferth\*, Joanne M. Schwark and Regina M. Stewart

Department of Chemistry  
Massachusetts Institute of Technology  
Cambridge, Massachusetts 02139



|                    |                                     |
|--------------------|-------------------------------------|
| Accession For      |                                     |
| NTIS CRA&I         | <input checked="" type="checkbox"/> |
| DTIC TAB           | <input type="checkbox"/>            |
| Unannounced        | <input type="checkbox"/>            |
| Justification      |                                     |
| By                 |                                     |
| Distribution       |                                     |
| Availability Codes |                                     |
| Dist               | Avail and/or Special                |
| A-1                |                                     |

**ABSTRACT**

The action of organoalkali reagents (RLi, RLi/Me<sub>3</sub>CONa, RLi/Me<sub>3</sub>COK) on cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> and cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub> results in ring opening to give alkali metal amides of the type RMe<sub>2</sub>SiNMeSiMe<sub>2</sub>NMeM (M = Li, Na, K) which react with chlorosilanes, R'Me<sub>2</sub>SiCl, to give the expected linear trisilazanes. Relatively unhindered lithium amides also open the cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> ring. The use of a catalytic amount of RLi or RLi/Me<sub>3</sub>CONa (but not of RLi/Me<sub>3</sub>COK) results in ring opening polymerization of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> but not of the more hindered cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub>.



## INTRODUCTION

Stoichiometric and catalytic ring opening of cyclotrisiloxanes by the action of strong nucleophilic reagents ( $\text{OH}^-$ ,  $\text{OR}^-$ ,  $\text{OSiMe}_3^-$ ,  $\text{RLi}$ , etc.) is well known,<sup>1</sup> and the catalytic processes are useful in the preparation of linear polysiloxanes. Applied to cyclopolysilazanes,  $\text{cyclo}-(\text{R}^1\text{R}^2\text{SiNR}^3)_n$ , such processes might be expected to result in formation of linear polysilazanes. However, none have been reported thus far.<sup>2</sup> Our interest in polysilazanes as precursors for silicon nitride and silicon carbonitride<sup>3</sup> led us to investigate the possibility of organoalkali reagent-catalyzed ring opening polymerization of cyclic polysilazanes.

## RESULTS AND DISCUSSION


In the cyclopolysiloxane series,  $\text{cyclo}-(\text{R}_2\text{SiO})_n$ , the four-membered ring is known only when R is an extremely bulky organic group<sup>4</sup> and for the  $\text{R} = \text{CH}_3$  series the cyclotrisiloxane is the smallest ring known. Hexamethylcyclotrisiloxane has enhanced reactivity, compared with the larger cyclics, and is readily cleaved by strong nucleophiles.<sup>1</sup> In the cyclopolysilazane series the four-membered-cyclodisilazane ring system is very stable, and many examples of  $\text{Si}_2\text{N}_2$  rings have been reported.<sup>5</sup>

Before investigating the possibility of the catalytic ring opening polymerization of cyclodisilazanes we have studied the stoichiometric opening of the cyclodisilazane ring by organoalkali reagents. The cyclodisilazanes chosen for study were 1 and 2.

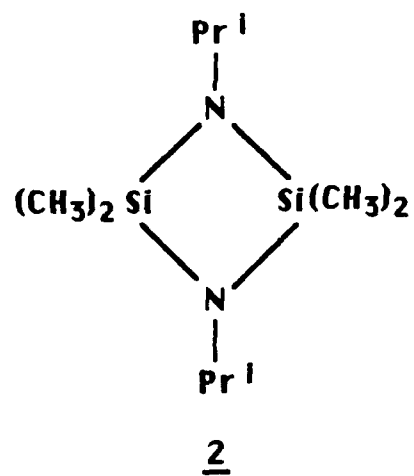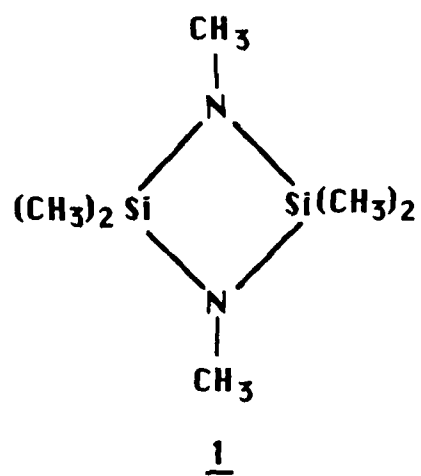


Both compounds are stable, distillable liquids. Hexamethylcyclodisilazane was found in a gas phase electron diffraction study to contain a planar  $\text{Si}_2\text{N}_2$  ring, with an  $\text{SiNSi}$  angle of  $98^\circ$  and an  $\text{Si-N}$  bond distance of  $1.74\text{\AA}$ ,<sup>6</sup> very similar to  $\text{SiNSi}$  bond angles and  $\text{Si-N}$  bond lengths of solid cyclodisilazanes as determined by X-ray diffraction.<sup>7</sup> It has been noted<sup>5c</sup> that the cyclodisilazane ring is quite strained compared with the six-membered cyclotrisilazane and the eight-membered cyclotetrasilazane rings. In view of this, one might expect that attack at a silicon atom of these cyclodisilazanes by a strongly nucleophilic organoalkali reagent will result in opening of the strained  $\text{Si}_2\text{N}_2$  ring.

There has been one previous report of the cleavage of a cyclodisilazane by an organolithium reagent (eq. 1).<sup>8</sup> In our study of

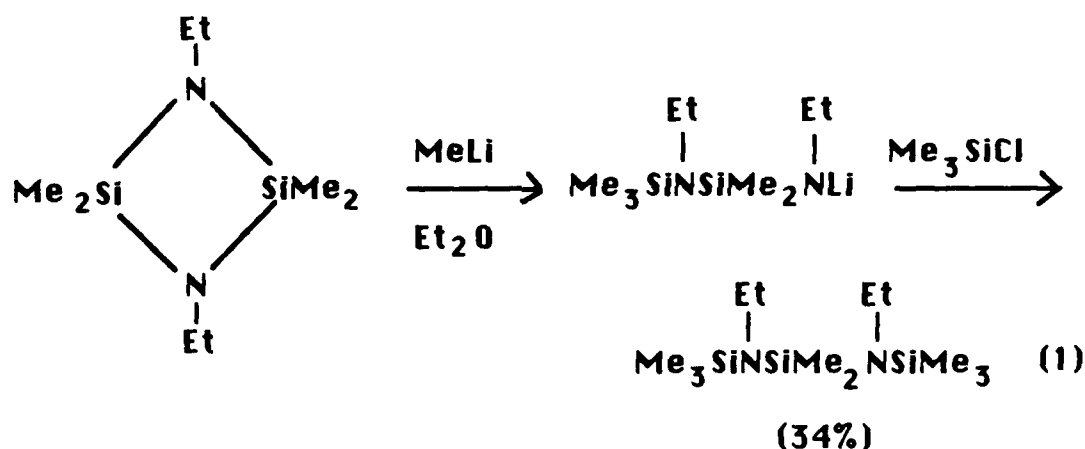

such ring opening reactions we found such reactions of 1 and 2 to be fairly general in terms of the alkyllithium reagent that may be used ( $\text{MeLi}$ ,  $n\text{-BuLi}$ ,  $t\text{-BuLi}$ ) and to proceed in high yield when carried out in THF solution (Table I and Scheme 1). In all reactions, the cyclodisilazane was added to a two- to fourfold excess of the respective organolithium reagent solution which had been cooled to a suitably low temperature (to minimize reaction of  $\text{RLi}$  with the solvent). The final reaction temperature depended on the lithium reagent used. Reactions with the reactive  $n$ - and  $t$ -butyllithium could be carried out at  $0^\circ\text{C}$ , but reactions with the less reactive methyllithium sometimes were carried out at room temperature or by heating briefly at reflux. The final quench with a chlorosilane was carried out at room


temperature or at reflux. In contrast to the facile ring opening of cyclo-(Me<sub>2</sub>SiO)<sub>3</sub> by organolithium reagents and other strong nucleophiles,<sup>1</sup> cyclo-(Me<sub>2</sub>SiNMe)<sub>3</sub> did not react with n-butyllithium in THF.

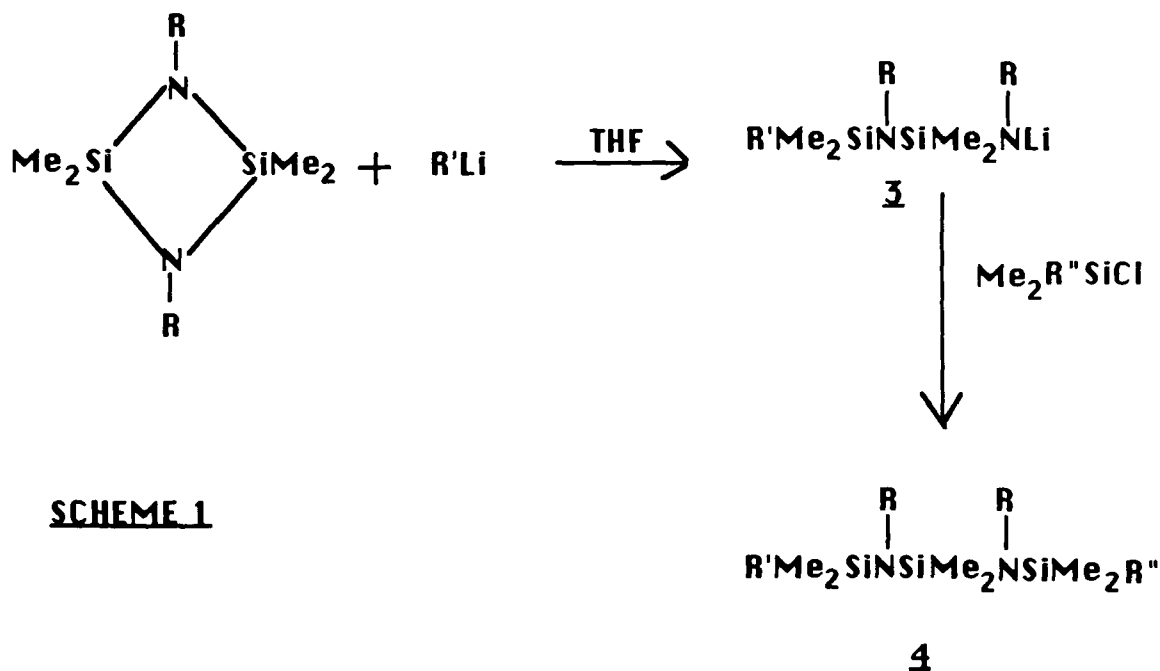


**SCHEME 1**

If cyclodisilazane ring opening is to be a useful oligomerization/polymerization procedure, the propagation steps involving further cyclodisilazane cleavage by lithium amide **3** and by higher oligomers and then polymers, i.e., by R'[Me<sub>2</sub>SiN(R)SiMe<sub>2</sub>N(R)]<sub>n</sub>Li in the case of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub>, must occur at a reasonable rate. Such ring opening reactions were examined first in stoichiometric reactions (Scheme 2). They were found to proceed in good yield (R,R' = Me, 70%; R = Me; R' = Me<sub>3</sub>Si, 83%) when the lithium amide was not too hindered and when the reaction mixture was heated at reflux. More hindered lithium amides such as iPr<sub>2</sub>NLi and (Me<sub>3</sub>Si)<sub>2</sub>NLi did not react with hexamethylcyclodisilazane. More to the point, a reaction of the initially formed methyllithium ring opening product, Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeLi, with a second molar equivalent of hexamethylcyclodisilazane, i.e., the first propagation step, gave the expected Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>2</sub>NMeSiMe<sub>2</sub>NMeLi and addition of Me<sub>3</sub>SiCl to the reaction mixture resulted in formation of Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>3</sub>

(4% yield) and  $\text{Me}_3\text{Si}(\text{NMeSiMe}_2)_3\text{NMeSiMe}_3$  (25% yield), as well as higher, nonvolatile oligomers. Thus we could expect such polymerization to occur, at least with  $\text{cyclo}-(\text{Me}_2\text{SiNMe})_2$ .

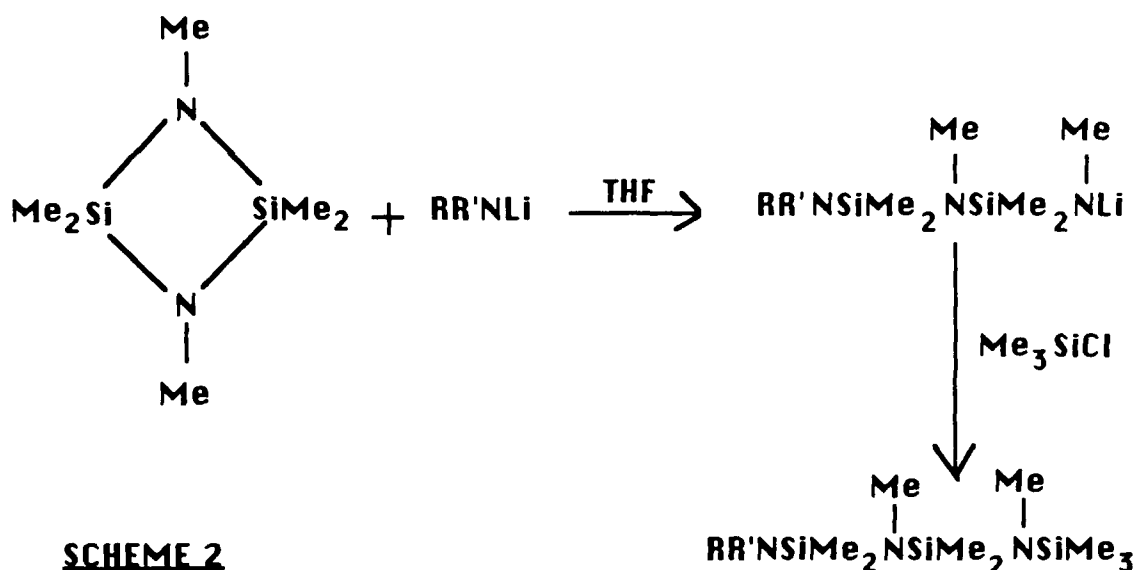

The initial ring-opening products, the lithium amides **3**, appeared to be stable in solution, even in refluxing THF, at least for limited periods of time. A potential decomposition process of the type described by Fink<sup>9</sup> (eq. 2) was not observed. Apparently higher temperatures are required for such a cycloreversion process.

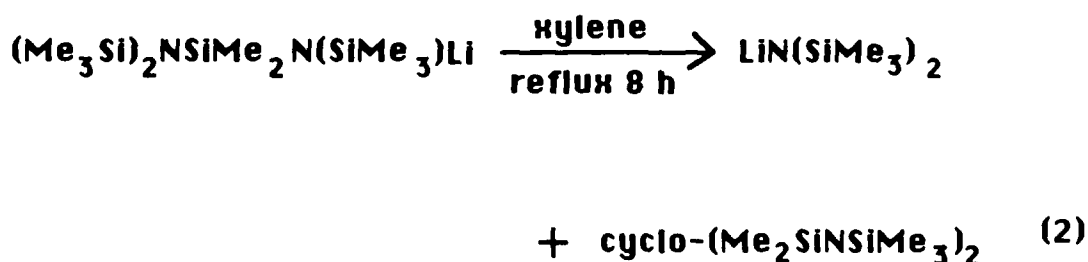

Lithium amide intermediates of type **3** could be observed by  $^{29}\text{Si}$  NMR spectroscopy. A solution of  $\text{Me}_3\text{SiNMeSiMe}_2\text{NMeLi}$  in which most of the THF had been removed by trap-to-trap distillation *in vacuo* and replaced by

$C_6D_6$  showed the  $^{29}Si$  resonance (DEPT technique<sup>10</sup>) for the  $Me_3SiN$  silicon atom at  $\delta_{Si}$  2.53 and the  $NSiMe_2NLi$  resonance at  $\delta_{Si}$  -7.74. By comparison, the  $Me_3SiCl$  quench product of this lithium amide,  $Me_3SiNMeSiMe_2NMeSiMe_3$  showed two  $^{29}Si$  resonances at the  $\delta_{Si}$  5.35 ( $Me_3Si$ ) and -0.26 ( $SiMe_2$ ). (Hexamethylcyclodisilazane in  $C_6D_6$  shows a single  $^{29}Si$  resonance at 8.01 ppm). The  $^{29}Si$  NMR spectra of this lithium amide and of  $n-BuMe_2SiNMeSiMe_2NMeLi$  [ $\delta_{Si}$  = 3.96 ( $nBuMe_2SiN$ ) and -9.61 ( $NSiMe_2N$ )] were devoid of other resonances, an indication that a clean ring opening had taken place.

Organosodium and -potassium reagents in general are more reactive than organolithium reagents, so it was of interest to study the action of organosodium and -potassium nucleophiles on hexamethylcyclodisilazane. The sodium reagents chosen were of the Lochmann base type,<sup>11</sup>  $RLi/Me_3CONa$ . ( $R = n-Bu, Me$ ). These react readily with hexamethylcyclodisilazane to give  $RMe_2SiNMeSiMe_2NMeNa$  below room temperature. Subsequent reaction of these sodium amide intermediates with a chlorosilane gave good yields of linear trisilazanes.

Organopotassium reagents of the  $MeLi/Me_3COK$  type<sup>11</sup> also reacted with hexamethylcyclodisilazane under mild conditions (-15°C). Addition of  $Me_3SiCl$  to such a reaction mixture gave  $Me_3SiNMeSiMe_2NMeSiMe_3$  in 60% yield, in addition to some nonvolatile material.

Since stoichiometric ring opening of cyclo- $(Me_2SiNMe)_2$  by  $RLi$ ,  $RNA$  and  $RK$  could be readily effected and since such cyclodisilazane ring opening also occurred with  $Me_2NLi$  and  $Me_3Si(Me)NLi$ , we undertook a study of organoalkali-catalyzed ring-opening polymerization of **1** and **2**. The expected chemistry is shown in Scheme 3. If, as anticipated, the rate of initiation is much greater than the rates of the propagation steps, then the molecular weight of the product will be determined by the monomer/initiator molar ratio (in the absence of side reactions).

Catalytic ring opening polymerization of hexamethylcyclodisilazane by  $n$ -butyl- and methyllithium and -sodium did indeed occur. The required reaction temperatures reflected the reactivity of these organoalkali reagents in


the stoichiometric reactions. Thus, the RLi-initiated reactions were started at 0°C and then the reaction mixtures were heated at reflux (in THF) until no more cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> could be detected by GLC.. In the case of the RNa-initiated polymerizations, the cyclodisilazane was added to the RLi/Me<sub>3</sub>CONa reagent at -78°C and subsequently the reaction mixture was warmed to -15°C and finally to room temperature. The products in general were white waxy solids. Their molecular weights, determined by cryoscopy in benzene, were in the 1000 - 3000 range and in most cases were not too far off from the theoretical molecular weight calculated from the monomer/catalyst molar ratio. However, cryoscopic molecular weights in that range are only approximate and no useful quantitative data are in hand. However, it is clear that ring-opening polymerization of hexamethylcyclodisilazane has been effected. Polymers of type RMe<sub>2</sub>SiNMe(SiMe<sub>2</sub>NMe)<sub>n</sub>SiMe<sub>2</sub>R' with n = about 11 to 35 have been prepared.

The oligomeric/polymeric products obtained must be linear species of the type shown in Scheme 3. For instance, the <sup>1</sup>H NMR spectrum (in CDCl<sub>3</sub>) of the wax obtained by the action of 5 mole % n-BuLi/Me<sub>3</sub>CONa on cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> (Me<sub>3</sub>SiCl quench) showed only two resonances at δ 0.12 (SiCH<sub>3</sub>) and 2.40 (NCH<sub>3</sub>). The n-C<sub>4</sub>H<sub>9</sub> resonances were observed only when the spectrum intensity was increased by several orders of magnitude. The <sup>29</sup>Si NMR spectrum in CDCl<sub>3</sub> of the wax showed a single resonance at δ<sub>Si</sub> -2.27. In contrast, the <sup>29</sup>Si NMR spectrum (in CDCl<sub>3</sub>) of the product obtained by the action of 10 mole % MeLi/Me<sub>3</sub>CONa on cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> (Me<sub>3</sub>SiCl quench), which was of lower molecular weight (1425-1500), showed the resonances due to the terminal Me<sub>3</sub>Si groups (5.17 ppm), the Me<sub>2</sub>Si next to the Me<sub>3</sub>Si groups (-1.53 ppm) and the Me<sub>2</sub>Si groups further inward (-2.25 ppm). These values should be compared with the <sup>29</sup>Si NMR spectrum of Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>2</sub>NMeSiMe<sub>2</sub>NMeSiMe<sub>2</sub>NMeSiMe<sub>3</sub> which was isolated as a pure compound and, in CDCl<sub>3</sub> solution, showed <sup>29</sup>Si resonances at δ<sub>Si</sub> 4.97, -1.46 and -2.63).


It would appear that in the case of RK initiation of the ring-opening polymerization of hexamethylcyclodisilazane the propagation process (Scheme 3) is complicated by "back-biting" of the reactive potassium amide chain terminus, a process which results in extrusion of cyclo-(Me<sub>2</sub>SiNMe)<sub>3</sub> as shown in Scheme 4 in its simplest form. Presumably, only the potassium

### SCHEME 3

#### Initiation





#### Propagation



("living polymer")

#### Termination

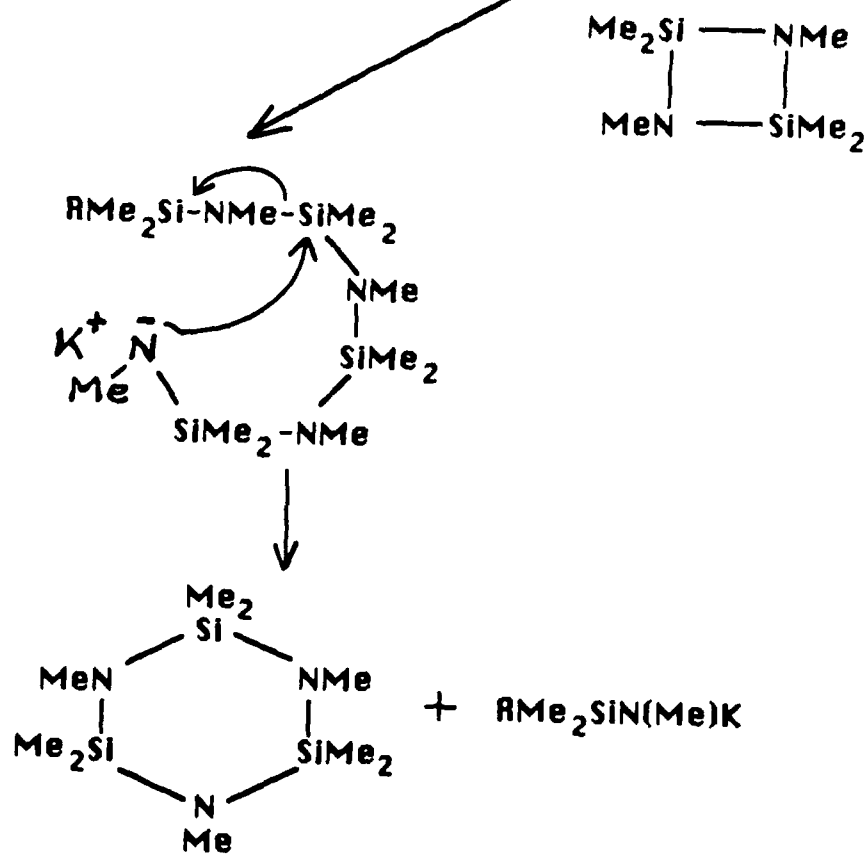

$$\begin{array}{c} \text{Me}_2\text{Si} - \text{NMe} \\ | \quad \quad | \\ \text{MeN} - \text{SiMe}_2 \end{array} + \text{RK} \xrightarrow{\text{THF}} \text{RMe}_2\text{SiNMeSiMe}_2\text{N(Me)K}$$


**etc.**

amide chain end (*vs.* lithium or sodium amide) is reactive enough to effect such nucleophilic chain scission.

The chemistry of the organoalkali-initiated ring opening polymerization of hexamethylcyclodisilazane does not appear to be a general process. The  $R_2NLi$  stoichiometric ring opening of cyclo-(MeSiNMe)<sub>2</sub> is, as mentioned above, subject to steric hindrance. Thus, it was not surprising that attempted ring opening polymerization of cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub> by 5 mole % *n*-BuLi in THF at room temperature, then at reflux, was unsuccessful. Obviously, the initially formed  $R'SiMe_2NPr^iSiMe_2N(Pr^i)Li$  intermediate is too hindered, so initiation is not followed by the propagation steps. Although this was not investigated, one would expect that bulky substituents on silicon also would prevent ring opening polymerization of cyclodisilazanes by RLi.

Linear organosilicon polymers do not give ceramic residues in high yield when they are pyrolyzed if they do not contain functional substituents whose thermally induced reactions lead to extensive cross-linking during the initial stages of pyrolysis. Linear polysilazanes of the type prepared in this study do not contain such substituents and thus it was not surprising that, as the TGA trace in Figure 1 shows, there is no ceramic residue when they are pyrolyzed. Thus, as expected, linear polysilazanes with an  $R_2SiNR'$  repeat unit are not useful preceramic polymers. Trapping of the volatile pyrolysis products of a  $Me_3Si[NMeSiMe_2]_xNMeSiMe_3$  polymer showed them to consist of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> and cyclo-(Me<sub>2</sub>SiNMe)<sub>3</sub>, with the former predominating. The formation of these small cyclics can be rationalized either in terms of (a) a radical chain scission/back-biting process or (b) of a decomposition to give an unsaturated  $Me_2Si=NMe$  intermediate which then undergoes cycloaddition. It may be that the cyclic trimer is formed by process (a) and the cyclic dimer by process (b).

## EXPERIMENTAL

### General Comments.

All reactions were performed under a nitrogen atmosphere using standard Schlenk techniques or a nitrogen-filled Vacuum Atmospheres dry box. All solvents were distilled under nitrogen from the appropriate drying agents. Chlorosilanes were purchased from Petrarch Systems, Inc. or Silar, and distilled from magnesium chips before use. Methyl- and t-butyllithium were purchased from Aldrich. Organolithium reagents were titrated for RLi content by the Gilman double titration method. Unsolvated potassium tert-butoxide (Aldrich) and sodium tert-butoxide (Alfa) were used as received.

Gas chromatographic (GLC) analyses were performed on a Hewlett-Packard 5890A gas chromatograph equipped with a 6 ft, 0.25 in column packed with 10% SE-30 silicone rubber gum on Chromosorb P. The internal standard method was used in yield determinations with a temperature program of 6°C/min from 100-275°C. Internal standards used were octane (C<sub>8</sub>), nonane (C<sub>9</sub>), decane (C<sub>10</sub>). Preparative GLC (Gow Mac 550 Thermal Conductivity Detector Gas Chromatograph, 6 ft, 0.25 in 10% SE-30 on Chromosorb P column) was used to collect samples for analysis and spectroscopy.

Proton NMR spectra were obtained either with a Jeol FX-90Q, a Bruker WM-250 or Varian XL-300 NMR spectrometer using CDCl<sub>3</sub>/CHCl<sub>3</sub> as a reference at 7.24 ppm downfield from tetramethylsilane. <sup>29</sup>Si NMR spectra (fully proton decoupled) were obtained using a Varian XL-300 operating at 59.59 MHz in CDCl<sub>3</sub> or C<sub>6</sub>D<sub>6</sub> with 0.05 M Cr(acac)<sub>3</sub> as a relaxation reagent. Tetramethylsilane (at 0.00 ppm) was used as an external standard. As indicated in the experiments below, some <sup>29</sup>Si NMR spectra were obtained using a DEPT pulse sequence.<sup>10</sup>

Molecular weights were determined by cryoscopy in benzene at M.I.T. or by vapor pressure osmometry by Galbraith Laboratories, Knoxville, TN. Elemental analyses were performed by the Scandinavian Microanalytical Laboratory, Herlev, Denmark.

For the polymers, the "theoretical" analytical values are those calculated on the basis of the experimental molecular weights. Since the latter were only approximate, the agreement between calculated and found analytical values was not always good.

#### Preparation of Starting Materials.

(a) **Dimethylbis(methylamino)silane.** A 1 l, three-necked flask equipped with a septum, an overhead mechanical stirrer and a cold condenser (Dry Ice/acetone) was flame-dried under nitrogen and charged with 85.1 g (0.66 mol) of  $\text{Me}_2\text{SiCl}_2$  and 400 ml of diethyl ether and cooled to  $0^\circ\text{C}$ . Gaseous methylamine (Matheson) was bubbled into the solution through a 6 in. stainless steel needle during the course of 3 h. The reaction mixture was allowed to warm to room temperature overnight. The precipitated  $[\text{MeNH}_3]\text{Cl}$  was filtered under nitrogen and washed with two 50 ml portions of ether. The combined organic phase was distilled to remove the  $\text{Et}_2\text{O}$ . The residue was distilled (1 ft. Vigreux column) to give 48.8 g (63%) of  $\text{Me}_2\text{Si}(\text{NHMe})_2$ , bp  $109^\circ\text{C}$  (lit.<sup>12</sup> bp  $57\text{--}58^\circ\text{C}$  at 132 mm Hg).

$^1\text{H}$  NMR (90 MHz,  $\text{CDCl}_3$ ):  $\delta$  -0.07 (s, 6H,  $\text{Me}_2\text{Si}$ ), 0.44 (broad s, 2H, NH), 2.41 (s, 6H, NMe).

#### (b) Dimethylbis(isopropylamino)silane.

A similar reaction in which 26.2 g (0.2 mol) of  $\text{Me}_2\text{SiCl}_2$  was added to 52.7g (0.89 mol) of isopropylamine (Aldrich, distilled from  $\text{CaO}$ ) in 400 ml of  $\text{Et}_2\text{O}$  gave 28.9 g (82%) of  $\text{Me}_2\text{Si}(\text{NHPr}^i)_2$  bp  $44^\circ\text{C}/10$  mm Hg). (lit.<sup>13</sup> bp  $47\text{--}48^\circ\text{C}/11$  mm Hg).

$^1\text{H}$  NMR (90 MHz,  $\text{CDCl}_3$ ):  $\delta$  -0.02 (s, 6H,  $\text{Me}_2\text{Si}$ ), 1.02 (d,  $J = 6.7$  Hz, 12H,  $\text{Me}_2\text{C}$ ), 3.20 (broad m, 2H,  $\text{NCH}$ ).

#### (c) Hexamethylcyclodisilazane.

A 1 l three-necked flask equipped with a mechanical stirrer, a condenser topped with a gas inlet tube (connecting to an oil bubbler in a Schlenk line), and a septum was flame dried and charged with 24.73 g (0.21

mol) of  $\text{Me}_2\text{Si}(\text{NHMe})_2$  and 62 ml of hexane. By means of a 250 ml addition funnel 277 ml of 1.51 M "halide-free" methyllithium (0.42 mol) was added at  $0^\circ\text{C}$ , dropwise over 2 h. After the mixture had been stirred at  $0^\circ\text{C}$  for 2 h, 26.9 g (0.21 mol) of  $\text{Me}_2\text{SiCl}_2$  was added dropwise at  $0^\circ\text{C}$ . The reaction mixture was stirred and heated at reflux for 24 h. Filtration (or centrifugation) removed the  $\text{LiCl}$ . Removal of the solvent by trap-to-trap distillation (room temperature, 70 mm Hg) was followed by distillation of the product, 23.8 (65%) of cyclo- $(\text{Me}_2\text{SiNMe})_2$ , bp  $50^\circ\text{C}/50\text{mm Hg}$  or  $60\text{--}62^\circ\text{C}$  at 70 mm Hg (lit.<sup>12</sup> bp  $52\text{--}52.5^\circ\text{C}$  at 51 mm Hg).

$^1\text{H}$  NMR (90 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.12 (s, 12H,  $\text{SiMe}_2$ ), 2.42 (s, 6H, MeN).  $^{13}\text{C}$  NMR (67.9 MHz,  $\text{C}_6\text{D}_6$ ):  $\delta_c$  0.44 (q,  $J=117.0$  Hz,  $\text{Me}_2\text{Si}$ ), 26.87 (q,  $J=134.9$  Hz, MeN).  $^{29}\text{Si}$  NMR (59.59 MHz,  $\text{C}_6\text{D}_6$ , DEPT):  $\delta_{\text{Si}}$  8.06 IR (thin film): 2955(m), 2900(s), 2810(s), 1435(vw), 1250(vs), 1190(vs), 860(vs), 840(sh), 785(vs), 675(vw),  $\text{cm}^{-1}$ .

**(d)  $N,N'$ -Diisopropyltetramethylcyclodisilazane.**

The reaction flask was charged with 15.06 g (0.086 mol) of  $\text{Me}_2\text{Si}(\text{NHPr}^i)_2$  and 250 ml of  $\text{Et}_2\text{O}$ .  $n$ -Butyllithium (65 ml of 2.68M in hexane, 0.173 mol) was added. After the resulting solution had been heated at reflux for 30 min, 11.2 g (0.087 mol) of  $\text{Me}_2\text{SiCl}_2$  was added. The reaction mixture was stirred and heated at reflux for 3 h, then was centrifuged to separate the  $\text{LiCl}$ . The organic layer, after removal of the  $\text{Et}_2\text{O}$ , was distilled (1 ft Vigreux column) to give 16.3 g (82%) of cyclo- $(\text{Me}_2\text{SiNPr}^i)_2$ , bp  $48.5/2.5$  mm Hg.

$^1\text{H}$  NMR (90 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.19 (s, 12H,  $\text{Me}_2\text{Si}$ ), 1.01 (d,  $J=6.3$  Hz, 12H,  $\text{Me}_2\text{C}$ ), 3.19 (sept,  $J=6.3$  Hz, 2H, NCH), which agrees with the literature.<sup>15</sup>

## Reaction of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> with Methyllithium.

### (a) Trimethylchlorosilane Quench

A 50 ml three-necked, round-bottomed flask equipped with a condenser topped with a gas inlet/outlet tube connected to an oil bubbler in a Schlenk line, a stir-bar, a glass stopper, and a septum (henceforth, the "standard reaction apparatus") was flame-dried and charged with 30 ml of THF and 13.0 ml of 1.51 M methyllithium (LiBr complex) (19.6 mmol) in diethyl ether. This solution was heated to reflux and 0.873 g (5.0 mmol) of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> was added dropwise by syringe during the course of 20 min. The resulting solution was heated at reflux for 25 min. and then 5.36 g (49.3 mmol) of Me<sub>3</sub>SiCl was added. The reaction mixture was stirred and heated at reflux for 30 min. At this point, a GLC yield determination was carried out. The solvent then was removed by trap-to-trap distillation (room temperature in vacuum). The residue was extracted with 20 ml of hexane and the extracts were filtered to remove LiCl. Distillation of the hexane left an oily residue from which the product was isolated by GLC (this is the "standard workup"). The GLC analysis (C<sub>8</sub> internal standard) showed the presence of one major product, identified as Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>3</sub>, in 70% yield.

Anal. Calcd. for C<sub>10</sub>H<sub>30</sub>N<sub>2</sub>Si<sub>3</sub>: C, 45.74; H, 11.51; N, 10.69. Found: C, 45.50; H, 11.33; N, 10.87.

<sup>1</sup>H NMR (90 MHz, CDCl<sub>3</sub>): δ 0.05 (s, 18H, Me<sub>3</sub>Si), 0.07 (s, 6H, Me<sub>2</sub>Si), 2.40 (s, 6H, MeN).

### (b) Dimethylchlorosilane Quench

The same procedure, with the exception that Me<sub>2</sub>SiHCl was the chlorosilane used, gave Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>2</sub>H in 83% yield.

Anal. Calcd. for C<sub>9</sub>H<sub>28</sub>N<sub>2</sub>Si<sub>3</sub>: C, 43.48; H, 11.35; N, 11.27. Found: C, 43.57; H, 11.39; N, 11.30.

<sup>1</sup>H NMR (90 MHz, CDCl<sub>3</sub>): δ 0.06 (s, 9H, Me<sub>3</sub>Si), 0.07 (s, 6H, NMe<sub>2</sub>SiN), 0.09 (d, J=3.4 Hz, 6H, Me<sub>2</sub>SiH), 2.39, 2.41 (both s, 6H, MeN), 4.42 (sept, J=3.4 Hz, Me<sub>2</sub>SiH).

(c) Dimethyldichlorosilane Quench

The same procedure was used except that  $\text{Me}_2\text{SiCl}_2$  (an excess) was the chlorosilane added at the end. The product,  $\text{Me}_3\text{SiNMeSiMe}_2\text{NMeSiMe}_2\text{Cl}$ , was obtained in 57% yield.

Anal. Calcd for  $\text{C}_9\text{H}_{27}\text{N}_2\text{Cl Si}_3$ : C, 38.19; H, 9.62; N, 9.90. Found: C, 38.54; H, 9.63; N, 9.92.

$^1\text{H}$  NMR (250 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.069 (s, 9H,  $\text{SiMe}_3$ ), 0.15 (s, 6H,  $\text{SiMe}_2$ ), 0.46 (s, 6H,  $\text{SiMe}_2\text{Cl}$ ), 2.42 (s, 3H, NMe), 2.49 (s, 3H, NMe).

Reaction of this compound with an excess of  $\text{CH}_3\text{NH}_2$  in hexane at  $-78^\circ\text{C}$  gave  $\text{Me}_3\text{SiNMeSiMe}_2\text{NMeSiMe}_2\text{NHMe}$  in 79% yield.

Anal. Calcd. for  $\text{C}_{10}\text{H}_{31}\text{N}_3\text{Si}_3$ : C, 43.26; H, 11.26; N, 15.13. Found: C, 43.43; H, 11.17; N, 15.11.

$^1\text{H}$  NMR (250 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.052 (s, 6H,  $\text{SiMe}_2$ ), 0.056 (s, 9H,  $\text{SiMe}_3$ ), 0.100 (s, 6H,  $\text{SiMe}_2$ ), 2.41 (s, 9H,  $\text{NCH}_3$ ).

**Reaction of cyclo-( $\text{Me}_2\text{SiNMe}$ ) $_2$  with n-Butyllithium.**

(a) Trimethylchlorosilane Quench

The standard reaction apparatus was charged with 30 ml of THF, cooled to  $0^\circ\text{C}$  and then 9.0 ml of 2.58M n-butyllithium (23.2 mmol) in hexane was added. Subsequently, 1.28 g (7.33 mmol) of cyclo-( $\text{Me}_2\text{SiNMe}$ ) $_2$  was added. The reaction mixture was stirred at  $0^\circ\text{C}$  for 30 min and then 4.29 g (39.5 mmol) of  $\text{Me}_3\text{SiCl}$  was added by syringe. The resulting reaction mixture, from which LiCl had precipitated, was warmed to room temperature. The standard workup followed. The product,  $\text{n-BuMe}_2\text{SiNMeSiMe}_2\text{NMeSiMe}_3$ , was obtained in 81% yield.

Anal. Calcd. for  $\text{C}_{13}\text{H}_{36}\text{N}_2\text{Si}_3$ : C, 51.24; H, 11.91; N, 9.19. Found: C, 51.30; H, 11.90; N, 9.38.

$^1\text{H}$  NMR (90MHz,  $\text{CDCl}_3$ ):  $\delta$  0.04 (s, 6H, n-Bu $\text{Me}_2\text{Si}$ ), 0.06 (s, 9H,  $\text{Me}_3\text{SiN}$ ), 0.08 (s, 6H,  $\text{NSiMe}_2\text{N}$ ), 0.68 - 1.42 (complex m, 9H, n-Bu), 2.40 (s, 6H, MeN),

(b) Dimethylchlorosilane Quench

The same procedure was used, but  $\text{Me}_2\text{SiHCl}$  was added to the end rather than  $\text{Me}_3\text{SiCl}$ . The product,  $n\text{-BuMe}_2\text{SiNMeSiMe}_2\text{-NMeSiMe}_2\text{H}$ , was obtained in 86% yield.

Anal. Calcd. for  $\text{C}_{12}\text{H}_{34}\text{N}_2\text{Si}_3$ : C, 49.76; H, 11.48; N, 9.67. Found: C, 49.73, H, 11.84; N, 9.44..

$^1\text{H}$  NMR (90 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.04(s, 6H,  $n\text{-BuMe}_2\text{Si}$ ), 0.07 (s, 6H,  $\text{NSiMe}_2\text{N}$ ), 0.10 (d,  $J = 2.9$  Hz, 6H,  $\text{SiMe}_2\text{H}$ ), 0.68-1.42 (complex m, 9H,  $n\text{-Bu}$ ), 2.39, 2.40 (both s, 6H,  $\text{MeN}$ ), 4.43 (complex m, 1H,  $\text{Me}_2\text{SiH}$ )

#### Reaction of cyclo- $(\text{Me}_2\text{SiNMe})_2$ with with $t\text{-Butyllithium}$ .

##### (a) Trimethylchlorosilane Quench

The standard reaction apparatus was charged with 30 ml of THF, and cooled to  $-78^\circ\text{C}$  (Dry Ice/ $\text{Me}_2\text{CO}$ ). and 10.0 ml of a 2.10M solution of  $t\text{-butyllithium}$  (21.0 mmol) in pentane was added. By syringe, 1.32 g (7.56 mmol) of cyclo- $(\text{Me}_2\text{SiNMe})_2$  was added. The mixture was stirred at  $-78^\circ\text{C}$  for 30 min and then the  $-78^\circ\text{C}$  bath was replaced with an ice bath. After the mixture had been stirred at  $0^\circ\text{C}$  for 30 min., 4.29 g (39.5 mmol) of  $\text{Me}_3\text{SiCl}$  was added. The reaction mixture was warmed to room temperature. The standard workup showed that the expected product,  $t\text{-BuMe}_2\text{SiNMeSiMe}_2\text{NMeSiMe}_3$ , had been formed in 87% yield.

Anal. Calcd. for  $\text{C}_{13}\text{H}_{36}\text{N}_2\text{Si}_3$ : C, 51.24; H, 11.91; N, 9.19. Found: C, 51.31; H, 11.91; N, 9.09.

$^1\text{H}$  NMR (90 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.05(s, 15H,  $t\text{-BuMe}_2\text{Si}$  and  $\text{Me}_3\text{Si}$ ), 0.10 (s, 6H,  $\text{NSiMe}_2\text{N}$ ), 0.86 (s, 9H,  $t\text{-Bu}$ ), 2.41, 2.44 (both s, 6H,  $\text{MeN}$ ).

### (b) Dimethylchlorosilane Quench

The same procedure, except that  $\text{Me}_2\text{SiHCl}$  was used instead of  $\text{Me}_3\text{SiCl}$ , gave  $t\text{-BuMe}_2\text{SiNMeSiMe}_2\text{NMeSiMe}_2\text{H}$  in 80% yield.

Anal. Calcd. for  $\text{C}_{12}\text{H}_{34}\text{N}_2\text{Si}_3$ : C, 49.76; H, 11.48; N, 9.67. Found: C, 49.60; H, 11.83; N, 9.41.

$^1\text{H}$  NMR (90 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.10 (d,  $J=3.2$  Hz, 6H,  $\text{Me}_2\text{SiH}$ ), 0.10 (s, 6H,  $t\text{-BuMe}_2\text{Si}$ ), 0.19 (s, 6H,  $\text{NSiMe}_2\text{N}$ ), 0.91 (s, 9H,  $t\text{-Bu}$ ), 2.32, 2.41 (both s, 6H,  $\text{MeN}$ ), 4.67 (sept,  $J = 3.2\text{Hz}$ , 1H,  $\text{Me}_2\text{SiH}$ ).

### Reaction of cyclo- $(\text{Me}_2\text{SiNMe})_2$ with Lithium Dimethylamide.

The standard reaction apparatus was charged with 20 ml of THF and cooled to  $-78^\circ\text{C}$  (Dry Ice/ $\text{Me}_2\text{CO}$ ). Dimethylamine (3ml liquid, 2.04 g, 0.045 mol) at  $-78^\circ\text{C}$  was cannulated into the reaction flask. By syringe, 3.70 ml of a 2.32M solution of  $n\text{-BuLi}$  (8.60 mmol) in hexane was added to this solution. The resulting  $\text{Me}_2\text{NLi}$  solution was warmed to room temperature, then was heated to reflux and 0.923 g (5.29 mmol) of cyclo- $(\text{Me}_2\text{SiNMe})_2$  was added by syringe, dropwise during the course of 20 min. The reaction mixture was cooled to room temperature and 1.03 g (9.47 mmol) of  $\text{Me}_3\text{SiCl}$  was added. The standard workup followed. The product,  $\text{Me}_2\text{NSiMe}_2\text{NMeSiMe}_2\text{NMeSiMe}_3$ , was obtained in 70% yield.

Anal. Calcd. for  $\text{C}_{11}\text{H}_{33}\text{N}_3\text{Si}_3$ : C, 45.30; H, 11.40; N, 14.41. Found: C, 45.02; H, 11.60; N, 14.36.

$^1\text{H}$  NMR (250 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.17 (s, 12H,  $\text{NSiMe}_2\text{N}$ ), 0.20 (s, 9H,  $\text{Me}_3\text{Si}$ ), 2.40, 2.42 (both s, 6H,  $\text{SiNMeSi}$ ), 2.44 (s, 6H,  $\text{Me}_2\text{N}$ ).

### Reaction of cyclo- $(\text{Me}_2\text{SiNMe})_2$ with Lithium N-Methyltrimethylsilylamide.

The standard reaction apparatus was charged with 20 ml of THF and 0.786 g (7.61 mmol) of  $\text{Me}_3\text{SiNHMe}$  and cooled to  $-78^\circ\text{C}$ . By syringe, 3.28 ml of a 2.32M solution of  $n\text{-BuLi}$  in hexane (5.15 mmol) was added. After the mixture had been stirred for 10 min at  $-78^\circ\text{C}$  it was warmed to room temperature and then heated to reflux. Hexamethylcyclodisilazane (0.9 g, 5.15 mmol) was added dropwise by syringe. After the mixture had been stirred for

30 min at reflux, 1.03 g (9.47 mmol) of  $\text{Me}_3\text{SiCl}$  was added. The standard workup followed. The product,  $\text{Me}_3\text{SiNMeSiMe}_2\text{NMeSiMe}_2\text{NMeSiMe}_3$ , was obtained in 83% yield.

Anal. Calcd. for  $\text{C}_{13}\text{H}_{39}\text{N}_3\text{Si}_4$ : C, 44.63; H, 11.24; N, 12.01. Found: C, 44.84; H, 11.18; N, 12.13.

$^1\text{H}$  NMR (90 MHz,  $\text{C}_6\text{D}_6$ ):  $\delta$  0.19 (s, 18H,  $\text{Me}_3\text{Si}$ ), 0.25 (s, 12H,  $\text{NSiMe}_2\text{N}$ ), 2.44 (s, 9H, MeN).

#### Reaction of cyclo- $(\text{Me}_2\text{SiNMe})_2$ with $\text{Me}_3\text{SiNMeSiMe}_2\text{NMeLi}$ .

The standard reaction apparatus was charged with 25 ml of THF and cooled to  $0^\circ\text{C}$ . By syringe, 3.0 ml of a 1.35M solution of methyllithium (4.05 mmol) in  $\text{Et}_2\text{O}$  was added. Subsequently, 0.711 g (4.08 mmol) of cyclo- $(\text{Me}_2\text{SiNMe})_2$  was added to the MeLi solution, dropwise over 10 min. The resulting solution was stirred for 20 min at  $0^\circ\text{C}$  and then for 30 min. at reflux. Another portion (0.60 g, 3.44 mmol) of cyclo- $(\text{Me}_2\text{SiNMe})_2$  then was added. After this solution had been heated for 30 min. at reflux, it was cooled to room temperature and 3.0 ml (23.7 mmol) of  $\text{Me}_3\text{SiCl}$  was added. After 30 min. at room temperature the standard workup was done. GLC analysis ( $\text{C}_9$  internal standard) showed the presence of two volatile products:  $\text{Me}_3\text{SiNMeSiMe}_2\text{NMeSiMe}_3$  (14%), identified by its  $^1\text{H}$  NMR spectrum (see above), and the pentasilazane,  $\text{Me}_3\text{SiNMeSiMe}_2\text{NMeSiMe}_2\text{NMeSiMe}_2\text{NMeSiMe}_3$  (25%). The latter was isolated by GLC and characterized.

Anal. Calcd. for  $\text{C}_{16}\text{H}_{48}\text{N}_4\text{Si}_5$ : C, 43.98; H, 11.07; N, 12.82. Found: C, 43.84; H, 11.00; N, 13.08.

$^1\text{H}$  NMR (250 MHz,  $\text{CDCl}_3$ ):  $\delta$  0.05 (s, 18H,  $\text{Me}_3\text{Si}$ ), 0.07 (s, 18H,  $\text{Me}_2\text{Si}$ ), 2.4 (s, 12H, MeN).

$^{29}\text{Si}$  NMR (59.59 MHz,  $\text{CDCl}_3$ ):  $\delta_{\text{Si}}$  -2.63 (s, 1 Si,  $\text{SiMe}_2$  central), -1.46 (s, 2 Si,  $\text{SiMe}_2$  first from end), 4.97 (s, 2 Si,  $\text{Me}_3\text{Si}$ ).

### Reaction of cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub> with Methyllithium.

The standard reaction apparatus was charged with 25 ml of THF and 2.50 ml. of a 1.66M solution of MeLi in Et<sub>2</sub>O (4.15 mmol). This solution was heated to reflux and 0.430 g (1.87 mmol) of cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub> was added. After the mixture had been stirred and heated at reflux for 30 min, 0.85 g (9.0 mmol) of Me<sub>2</sub>SiHCl was added. The standard workup followed. The product, Me<sub>3</sub>SiNPr<sup>i</sup>SiMe<sub>2</sub>NPr<sup>i</sup>SiMe<sub>2</sub>H, was obtained in 64% yield.

Anal. Calcd. for C<sub>13</sub>H<sub>36</sub>N<sub>2</sub>Si<sub>3</sub>: C, 51.26; H, 11.91; N, 9.20. Found: C, 51.37; H, 11.90; N, 9.32.

<sup>1</sup>H NMR (250 MHz, CDCl<sub>3</sub>): δ 0.14 (s, 9H, Me<sub>3</sub>Si), 0.17 (d, J=3.6Hz, 6H, Me<sub>2</sub>SiH), 0.19 (s, 6H, NSiMe<sub>2</sub>N), 1.15 (d, J=6.7Hz, 6H, Me<sub>2</sub>CH), 1.17 (d, J=6.7Hz, 6H, Me<sub>2</sub>CH), 3.46 (sept, J=6.7Hz, 2H, Me<sub>2</sub>CH), 4.53 (sept, J = 3.7 Hz, Me<sub>2</sub>SiH).

### Reaction of cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub> with n-Butyllithium.

Using the same procedure, the reaction of 0.865 g (3.76 mmol) of cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub> in 25 ml of THF with 4.20 mmol of n-BuLi in hexane was carried out at room temperature. Addition of 0.87 g (9.20 mmol) of Me<sub>2</sub>SiHCl and the standard workup followed. The product, n-BuMe<sub>2</sub>SiNPr<sup>i</sup>SiMe<sub>2</sub>NPr<sup>i</sup>SiMe<sub>2</sub>H, was obtained in 67% yield.

Anal. Calcd. for C<sub>16</sub>H<sub>42</sub>N<sub>2</sub>Si<sub>3</sub>: C, 55.42; H, 12.21; N, 8.08. Found: C, 55.34; H, 12.14; N, 8.20.

<sup>1</sup>H NMR (250 MHz, CDCl<sub>3</sub>): δ 0.13 (s, 6H, n-BuMe<sub>2</sub>Si), 0.17 (d, J = 3.6 Hz, 6H, Me<sub>2</sub>SiH), 0.20 (s, 6H, NSiMe<sub>2</sub>N), 0.60 - 1.42 (complex m, 9H, n-Bu), 1.15, 1.17 (both d, J=6.7Hz, 12H, Me<sub>2</sub>CH), 3.47 (sept, J=6.7Hz, 12H, Me<sub>2</sub>CH), 4.53 (sept, J=3.6 Hz, 1H, Me<sub>2</sub>SiH).

A trimethylchlorosilane quench of such a cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub>/n-BuLi reaction mixture gave n-BuMe<sub>2</sub>SiNPr<sup>i</sup>SiMe<sub>2</sub>NPr<sup>i</sup>SiMe<sub>3</sub> in 60% yield.

Anal. Calcd. for C<sub>17</sub>H<sub>44</sub>N<sub>2</sub>Si<sub>3</sub>: C, 56.59; H, 12.29; N, 7.76. Found: C, 56.50; H, 12.28; N, 7.84.

<sup>1</sup>H NMR (250 MHz, CDCl<sub>3</sub>): δ 0.14 (s, 6H, n-BuMe<sub>2</sub>Si), 0.15 (s, 9H, Me<sub>3</sub>Si), 0.21 (s, 6H, NSiMe<sub>2</sub>N), 0.60 - 1.42 (complex m, 9H, n-Bu), 1.17 (d, J=6.0Hz, 12H, Me<sub>2</sub>CH), 3.52, 3.57 (both sept, J=6.0 Hz, 2H, Me<sub>2</sub>CH).

### Attempted Reaction of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> with Lithium Bis(trimethylsilyl)amide.

The standard reaction apparatus was charged with 20 ml of THF, and 2.50 ml. of (Me<sub>3</sub>Si)<sub>2</sub>NH (1.93 g, 0.012 mol) and cooled to -78°C in a dry ice/acetone bath. By syringe, 4.50 ml of a 2.66M solution of n-butyllithium (12.0 mmol) in hexane was added over 5 min. The dry ice/acetone bath was removed after 15 min and the reaction mixture was warmed to room temperature, then heated to reflux. By syringe, cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> (0.961 g, 5.51 mmol) was added dropwise over 30 min. After an additional 16h at reflux, the reaction mixture was cooled to room temperature and trimethylchlorosilane (1.58 ml, 1.36 g, 12.50 mmol) was added. A white precipitate formed. The GLC analysis (internal standard C<sub>9</sub>) of the reaction mixture showed the presence of unreacted (Me<sub>2</sub>SiNMe)<sub>2</sub> in 100% yield, which was identified by comparison of its <sup>1</sup>H NMR spectrum with that of an authentic sample.

### Reaction of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> with n-Butyllithium/Sodium t-Butoxide.

#### (a) Trimethylchlorosilane Quench

The standard apparatus, equipped also with a low temperature thermometer, was charged with 0.905 (9.42 mmol) of t-BuONa and 40 ml of THF, and, after cooling to -78°C, 3.66 ml of a 2.57M solution of n-BuLi in hexane (9.42 mmol). After 5 minutes, 0.816 g (4.68 mmol) of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> was added. The mixture was warmed to -15°C, at which point the cyclodisilazane dissolved. After 10 min trimethylchlorosilane (2.14 g, 19.7 mmol) was added and the reaction mixture was stirred at room temperature for 30 min. Standard workup showed the presence of n-BuMe<sub>2</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>3</sub> in 87% yield. The product had proton NMR and IR spectra identical with those of an authentic sample (see above).

(b) Vinyldimethylchlorosilane Quench

Essentially the same procedure as in (a) was used, except that only 10% of the cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> was added at -78°C and the rest at -15°C. Also, ViMe<sub>2</sub>SiCl was used in place of Me<sub>3</sub>SiCl. The product, n-BuMe<sub>2</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>2</sub>Vi, was obtained in 68% yield.

Anal. Calcd. for C<sub>14</sub>H<sub>36</sub>N<sub>2</sub>Si<sub>3</sub>: C, 53.09; H, 11.46; N, 8.84. Found: C, 52.92; H, 11.46; N, 9.23.

<sup>1</sup>H NMR (250 MHz, CDCl<sub>3</sub>): δ 0.04 (s, 6H, n-BuMe<sub>2</sub>Si), 0.08 (s, 6H, NSiMe<sub>2</sub>N), 0.13 (s, 6H, SiMe<sub>2</sub>Vi), 0.54 (t, 2H, n-PrCH<sub>2</sub>Si), 0.86 (t, 3H, CH<sub>3</sub> of n-Bu), 1.27(broad m, 6H, internal CH<sub>2</sub>CH<sub>2</sub> of n-Bu), 2.4 (s, 6H, MeN), 5.6 - 6.3 (complex m, 3H, CH<sub>2</sub>=CH)

## Reaction of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> with Methyllithium/Sodium t-Butoxide.

### (a) Trimethylchlorosilane Quench

The same procedure was used as in (b) immediately above except that methyllithium in Et<sub>2</sub>O was used in place of n-BuLi and Me<sub>3</sub>SiCl was the chlorosilane added. The product, Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>3</sub>, a known compound (see above), was obtained in 70% yield. Its <sup>1</sup>H NMR spectrum was identical with that reported above.

### (b) Vinyldimethylchlorosilane Quench

The same procedure as that was described immediately above was used, except that ViMe<sub>2</sub>SiCl was the chlorosilane used. The product, Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>2</sub>Vi, was obtained in 60% yield.

Anal. Calcd. for C<sub>11</sub>H<sub>30</sub>N<sub>2</sub>Si<sub>3</sub>: C, 48.10; H, 11.00; N, 10.20. Found: C, 48.09; H, 11.17; N, 10.55.

<sup>1</sup>H NMR (250 MHz, CDCl<sub>3</sub>): δ 0.05 (s, 9H, Me<sub>3</sub>Si), 0.08 (s, 6H, NSiMe<sub>2</sub>N), 0.13 (s, 6H, SiMe<sub>2</sub>Vi), 2.4 (s, 6H, MeN) 5.6 - 6.3 (complex m, 3H, CH<sub>2</sub>=CH).

## Reaction of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> with Methyllithium/Potassium t-Butoxide.

The standard apparatus was charged with 1.04 g (9.27 mmol) of t-BuOK and 30 ml of THF. To this solution, cooled to -78°, was added 17.0 ml of a 0.545M solution of MeLi in Et<sub>2</sub>O (9.27 mmol). After 5 min, one-tenth of a solution of 1.645g (9.43 mmol) of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> was added by syringe. The mixture then was warmed to -15°C and the rest of the cyclodisilazane solution was added. The resulting mixture was warmed to room temperature and now 1.20 g (11.1 mmol) of Me<sub>3</sub>SiCl was added. After 30 min., the standard workup gave 3.26 g of a clear, very viscous oily solid. This was diluted with THF and trap-to-trap distilled to give 2.1 g of a clear, yellowish liquid. GLC analysis showed Me<sub>3</sub>SiNMeSiMe<sub>2</sub>NMeSiMe<sub>3</sub> (see above) to be present in 60% yield.

## Ring-Opening Polymerization of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub>

### (1) With Organolithium Reagents.

The general procedure was as follows.

The standard reaction apparatus was charged with the solvent, cooled (either to 0°C or -78°C) and then the (Me<sub>2</sub>SiNMe)<sub>2</sub> was added by syringe. Subsequently, the organolithium reagent solution was added and the reaction mixture was stirred at room temperature and then at the reflux temperature for some hours. The chlorosilane, generally an excess, then was added to "kill" the living polymer (LiCl precipitated) and the mixture was stirred at room temperature for 30-60 min. Volatiles were removed at reduced pressure, leaving a white solid which then was extracted with 15-20 ml of hexane. The extracts were centrifuged to remove LiCl and the supernatant solution was distilled (trap-to-trap in vacuo), leaving, generally, a white, waxy solid. The latter was soluble in organic solvents such as hexane, benzene, chloroform, carbon tetrachloride and THF.

#### (a) 10% MeLi in THF.

Hexamethylcyclodisilazane (1.546 g, 8.9 mmol) and 0.66 ml of 1.35M (0.89 mmol) of MeLi in diethyl ether were allowed to react in 25 ml of THF (2.5 h. reflux). Trimethylchlorosilane (0.26 g, 2.4 mmol) was added. Work-up gave 1.148 g (75% yield) of a white, waxy solid.

Anal. Calcd: C, 42.33; H, 10.66; N, 14.81. Found: C, 40.65; H, 9.85; N, 14.02.

<sup>1</sup>H NMR (250 MHz, CDCl<sub>3</sub>): δ 0.11 (s, 2.2H, SiMe) 2.39 (s, 1 H, NMe). <sup>29</sup>Si NMR(59.59 MHz, DEPT, CDCl<sub>3</sub>): δ<sub>Si</sub> -2.18 (s, SiMe<sub>2</sub>), -1.4 (Me<sub>3</sub>SiNMeSiMe<sub>2</sub>-), 5.2 (s, SiMe<sub>3</sub>).

Mol. wt. (cryoscopy): 1140 (calcd. from monomer/RLi ratio: 1735)

#### (b) 5% Methyllithium in THF.

(Me<sub>2</sub>SiNMe)<sub>2</sub> (1.743 g, 9.99 mmol) and 0.39 ml of 1.30M MeLi (0.51 mmol) in Et<sub>2</sub>O were allowed to react in 25 ml of THF (mixed at -78°C, at reflux for 4 h); 1.72 g (15.8 mmol) of Me<sub>3</sub>SiCl was added. Work-up gave a white, waxy solid (1.65 g, 94% yield).

Mol. wt. (cryoscopy): 3000 - 3200 (calcd. from monomer/RLi ratio: 3400).

**(c) 5% n-Butyllithium in THF**

(Me<sub>2</sub>SiNMe)<sub>2</sub> (0.468 g, 2.68 mmol) and 53ml of 2.52M (0.13 mmol) of n-BuLi in hexane were allowed to react in 25 ml of THF, initially at -78°C, then, after slow warming, at reflux for 1 h. Dimethylchlorosilane (20 mg, 0.18 mmol) was added. Work-up gave 0.414 g (89%) of a white, waxy solid.

Anal. Calcd: C, 41.80; H, 10.00; N, 14.82. Found: C, 40.78; H, 9.39; N, 14.59.

<sup>1</sup>H NMR (300 MHz, C<sub>6</sub>D<sub>6</sub>): δ 0.36 (s, 2H, SiMe), 2.56 (s, 1H, NMe).

<sup>13</sup>C NMR (67.9 MHz, C<sub>6</sub>D<sub>6</sub>): δ<sub>C</sub> 1.94 (q, J = 118.3Hz, SiMe), 30.25 (q, J = 136.0 Hz, NCH<sub>3</sub>). <sup>29</sup>Si NMR (59.59 MHz, DEPT, C<sub>6</sub>D<sub>6</sub>): δ<sub>Si</sub> -1.82.

Mol. Wt.(VPO): 1500.

**(d) 10% n-Butyllithium in Hexane.**

(Me<sub>2</sub>SiNMe)<sub>2</sub> (1.831 g, 10.5 mmol) and 0.45 ml of 2.42M (1.1 mmol) of n-BuLi in hexane were allowed to react in 30 ml of hexane (initially at 0°C, then at reflux for 1 h). Trimethylchlorosilane (23.7 mmol) was added. Work-up gave 1.67 g (91%) of a white, waxy solid.

<sup>1</sup>H NMR (250 MHz, CDCl<sub>3</sub>): δ 0.12 (s, 6.2H, SiMe), 0.4 - 1.25 (complex m, 1H, C<sub>4</sub>H<sub>9</sub>), 2.39 (s, 2.8H, NMe).

Mol. Wt. (cryoscopy): 1020 (calcd: 1680).

## (2) With the RLi/Me<sub>3</sub>CONa Reagent.

The standard reaction apparatus was charged with the sodium tert-butoxide and the THF and the solution was cooled to -78°C. Subsequently, an equimolar quantity of the organolithium reagent was added and the mixture was stirred at -78°C for a few minutes. One-tenth of the total amount of the (Me<sub>2</sub>SiNMe)<sub>2</sub> to be added then was introduced by syringe. The Dry Ice/acetone bath was removed and the rest of the cyclodisilazane was added at -15°C over a period of 10 min. The reaction mixture was allowed to warm to room temperature and then an excess of a chlorosilane was added. After 30 min of stirring the volatiles were removed at reduced pressure. The residue was extracted with hexane. Centrifugation and removal of hexane at reduced pressure generally left a white waxy solid.

### (a) 10% MeLi/Me<sub>3</sub>CONa

(Me<sub>2</sub>SiNMe)<sub>2</sub> (2.036 g, 11.67 mmol), 0.11g (1.14 mmol) of Me<sub>3</sub>CONa and 2.1 ml of 1.35 M (1.14 mmol) of MeLi in Et<sub>2</sub>O were allowed to react in 25 ml of THF, initially at -78°C, then at room temperature. Trimethylchlorosilane (2.37 mmol) was added. Work-up gave 1.737 g (85%) of a white, waxy solid.

Anal. Calcd: C, 41.96; H, 10.56; N, 15.29; Si, 32.19. Found: C, 40.95; H, 9.38; N, 13.89; Si, 33.18.

<sup>1</sup>H NMR (250 MHz, CDCl<sub>3</sub>): δ 0.12 (s, 2.15H, SiMe), 2.39 (s, 1H, NMe). <sup>29</sup>Si NMR (59.59 MHz, DEPT, CDCl<sub>3</sub>): δ<sub>Si</sub> -2.25 (s, inner SiMe<sub>2</sub>), -1.53 (s, Me<sub>3</sub>SiNMeSiMe<sub>2</sub>-), 5.17 (s, SiMe<sub>3</sub>).

Mol. Wt. (cryscopy): 1425 -1500 (calcd: 1780). Ceramic yield (by TGA, to 950°C at 10°C/min. under argon): 0%.

In another such experiment, the living polymer was quenched with Me<sub>2</sub>(CH<sub>2</sub>=CH)SiCl to give a polymer with a SiMe<sub>2</sub>CH=CH<sub>2</sub> end-group as a white, waxy solid in 97% yield, mol. wt. 1960.

**(b) 10% n-BuLi/Me<sub>3</sub>CONa**

(Me<sub>2</sub>SiNMe)<sub>2</sub> (0.90 g, 5.2 mmol), 0.05 g (0.52 mmol) of Me<sub>3</sub>CONa and 0.20 ml of 2.57M (0.52 mmol) of n-BuLi in hexane were allowed to react in 30 ml of THF, initially at -78°C, then at room temperature. Trimethylchlorosilane (0.13 g, 0.12 mmol) was added. Work-up gave 0.833 g (93%) of a white, waxy solid.

Anal. Calcd: C, 42.94; H, 10.65; N, 14.95. Found: C, 41.91; H, 10.03; N, 14.03. <sup>1</sup>H NMR (300 MHz, CDCl<sub>3</sub>): δ 0.13 (s, 2H, SiMe), 2.40 (s, 1H, NMe); (400 MHz, C<sub>6</sub>D<sub>6</sub>): δ 0.35 (s, 2H, SiMe), 2.56 (s, 1H, NMe). <sup>29</sup>Si NMR (59.59 MHz, DEPT, CDCl<sub>3</sub>): δ<sub>Si</sub> -2.25; in C<sub>6</sub>D<sub>6</sub>, δ<sub>Si</sub> -1.79. Mol. Wt. (cryoscopic): 1580 (calcd. 1730).

A similar reaction in which Me<sub>2</sub>(CH<sub>2</sub>=CH)SiCl was used in place of Me<sub>3</sub>SiCl gave a white, waxy solid, molecular weight around 1550.

**(c) 5% n-BuLi/Me<sub>3</sub>CONa**

The same procedure as above was used except that 5% n-BuLi/Me<sub>3</sub>CONa (0.25 mmol/4.9 mmol of (Me<sub>2</sub>SiNMe)<sub>2</sub>) was used. A white, tacky solid (0.875 g, 100%) was obtained.

Anal. Calcd: C, 42.18; H, 10.53; N, 15.47. Found: C, 42.31; H, 9.89; N, 15.12. <sup>1</sup>H NMR (300 MHz, CDCl<sub>3</sub>): δ 0.12 (s, 2H, SiMe), 2.40 (s, 1H, NMe); (400 MHz, C<sub>6</sub>D<sub>6</sub>): δ 0.36 (s, 2H, SiMe), 2.56 (s, 1H, NMe). <sup>29</sup>Si NMR (59.59 MHz, CDCl<sub>3</sub>): δ<sub>Si</sub> -2.27 (in C<sub>6</sub>D<sub>6</sub>, -1.79).

**Reaction of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> with 20% n-Butyllithium/Potassium tert-Butoxide in THF, Trimethylchlorosilane Quench**

The standard reaction apparatus was charged with potassium tert-butoxide (0.054 g, 0.50 mmol) in the dry box, connected to a nitrogen line, and cooled to -78°C in a dry ice/acetone bath. By syringe, 15 ml of THF was added and then 0.21 ml of a 2.40 M solution of n-butyllithium (0.50 mmol) in hexane was added. After 5 min, cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> (0.428 g, 2.45 mmol) was added all at once. The cyclodisilazane was frozen in the reaction mixture. The bath was removed and the reaction mixture warmed until the

cyclodisilazane dissolved. The  $-78^{\circ}\text{C}$  bath was replaced and the reaction mixture cooled again to  $-78^{\circ}\text{C}$ . A GLC analysis of the reaction mixture showed no remaining cyclodisilazane, so trimethylchlorosilane (0.13 g, 1.20 mmol) was added and the bath was removed. The reaction mixture was warmed to room temperature and a white precipitate formed. The standard work-up was done. A GLC analysis (internal standard  $\text{C}_9$ ) of the reaction mixture showed the presence of one major product,  $(\text{Me}_2\text{SiNMe})_3$  (0.40 g, 1.5 mmol, 94% based on the conversion of three equivalents of the cyclodisilazane to two equivalents of the cyclotrisilazane), which was identified by comparison of its  $^1\text{H}$  NMR spectrum and melting point ( $34^{\circ}\text{C}$ , lit.<sup>12</sup>  $33\text{--}34^{\circ}\text{C}$ ) with those of an authentic sample.

#### Reaction of cyclo- $(\text{Me}_2\text{SiNMe})_2$ with 10% KH in THF

The standard reaction apparatus was charged with 30 ml of THF and 0.02 g of KH (0.5 mmol). By syringe cyclo- $(\text{Me}_2\text{SiNMe})_2$  (0.892 g, 5.11 mmol) was added over 20 min. After an additional 1 h at room temperature, the KH was still present as an insoluble solid in the reaction mixture which settled rapidly when the reaction mixture was not stirred. A GLC analysis of the supernatant solution showed that cyclo- $(\text{Me}_2\text{SiNMe})_2$  had completely reacted and a new product was present. Methyl iodide (1.0 ml, 2.28 g, 16.2 mmol) was added. No precipitate formed. A standard work-up of the reaction mixture was performed to remove the unreacted KH. The GLC analysis (internal standard  $\text{C}_{10}$ ) of the reaction mixture showed the presence of one major product, cyclo- $(\text{Me}_2\text{SiNMe})_3$  (0.895 g, 3.42 mmol, 89% based on the conversion of three equivalents of the cyclodisilazane to two equivalents of the cyclotrisilazane), which was GC-collected and identified by comparison of its  $^1\text{H}$  NMR spectrum and melting point ( $34^{\circ}\text{C}$ ; lit.<sup>12</sup>  $33\text{--}34^{\circ}\text{C}$ ) with those of an authentic sample. Another lower-boiling minor product was also present by GLC analysis, but in a quantity too small to collect and identify.

#### Attempted Polymerization of cyclo- $(\text{Me}_2\text{SiNPr}^i)_2$ with 5% Methyllithium in THF, Trimethylchlorosilane Quench.

The standard reaction apparatus was charged with 20 ml of THF and 0.972 g of cyclo-(Me<sub>2</sub>SiN<sup>i</sup>Pr)<sub>2</sub> (4.22 mmol) and the reaction mixture was heated to reflux. By syringe, 0.13 ml of a 1.59 M solution of methyllithium (0.21 mmol) in Et<sub>2</sub>O was added. After an additional 18h at reflux, trimethylchlorosilane (0.030 ml, 0.026 g, 0.21 mmol) was added. A white precipitate formed. The standard work-up of the reaction mixture was performed. The GLC analysis (internal standard C<sub>9</sub>) of the reaction mixture showed the presence of one major product, unreacted cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub> (0.885 g, 3.84 mmol, 91%), which was identified by comparison of its <sup>1</sup>H NMR spectrum with that of an authentic sample.

The same result was observed when n-butyllithium was used in place of methyllithium.

#### Pyrolysis of a Me(SiMe<sub>2</sub>NMe)<sub>x</sub>SiMe<sub>3</sub> Polymer

A 4.604 g sample of the polymer (mol. wt. 1425-1500) was divided between two silica boats and pyrolyzed in a stream of nitrogen in a Lindberg tube furnace equipped with a controller (30° to 300°C at 10°C/min; 30 min at 300°; 300°C to 700°C at 10°C/min). The exit end of the pyrolysis tube led to two traps which were immersed in liquid nitrogen. Upon completion of the pyrolysis the tubes were found to contain white solids. These were dissolved in diethyl ether. Evaporation of most of the ether at reduced pressure left a concentrated solution of the volatile pyrolysis products. This solution was examined by GLC. Two products were present. These were collected and yields were determined (n-nonane internal standard): cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> (38% yield) and (Me<sub>2</sub>SiNMe)<sub>3</sub> (12% yield). They were identified by comparison of their IR and <sup>1</sup>H NMR spectra with those of authentic samples.<sup>12</sup>

Acknowledgments The authors are grateful to the Office of Naval Research for support of this work.

## REFERENCES AND NOTES

1. Noll, W. "Chemistry and Technology of Silicones", Academic Press: New York, 1968, Chapter 5.
2. For a discussion of previous attempts to prepare linear polysilazanes containing  $R_2SiNR$  or  $R_2SiNH$  repeat units see: Aylett, B.J. Organomet. Chem. Rev. 1968, 3, 151.
3. Seyferth, D. in "Inorganic and Organometallic Polymers", (ACS Symposium Series 360), Zeldin, M.; Wynne, K.J.; Allcock, H.R., eds., American Chemical Society: Washington, D.C., 1988, pp. 143-155 and references cited therein.
4. Michalczyk, M.J.; Fink, M.J.; Haller, K.J.; West, R.; Michl, J. Organometallics 1986, 5, 531.
5. For reviews on cyclodisilazanes see:
  - (a) Fink, W. Angew Chem. Int. Ed. Engl. 1966, 5, 760
  - (b) Zhinkin, D.Ya., Varezkin, Yu.M.; Morgunova, M.M. Russ. Chem. Rev. 1980, 49, 1149.
  - (c) Varezkin, Yu.M.; Zhinkin, D.Ya.; Morgunova, M.M. Russ Chem Rev. 1981, 50, 1158.
  - (d) Klingebiel, U. Nachr. Chem. Tech. Lab. 1987, 35, 1042.
6. Gergo, E.; Schultz, G.; Hargittai, T. J. Organomet. Chem. 1985, 292, 343.
7. (a) Parkanyi, L.; Argay, G.; Hencsei, P.; Nagy, J. J. Organomet. Chem. 1976, 116, 299.
  - (b) Parkanyi, L.; Szollosy, A.; Bihatsi, L., Hencsei, P. J. Organomet. Chem. 1983, 251, 159.
  - (c) Parkanyi, L.; Szollosy, A.; Bihatsi, L.; Hencsei, P.; Nagy, J. J. Organomet. Chem. 1983, 256, 235.

- (d) Parkanyi, L.; Bihatsi, L.; Hencsei, P.; Szollosy, A. I. Organomet. Chem. 1987, 321, 7.
8. (a) Bush, R.P.; Lloyd, N.C.; Pearce, C.A. I. Chem. Soc. Chem. Commun. 1967, 1269.  
(b) Bush, R.P.; Pearce, C.A. I. Chem. Soc. (A) 1969, 808.
9. Fink, W. Chem. Ber. 1963, 96, 1071.
10. Williams, E.A., Cargioli, J.D., in Annual Reports on NMR Spectroscopy, Vol. 9, Webb, G.A., Ed., Academic Press, New York, 1979, pp. 221-318; Vol 15, 1983, pp. 235-289.
11. Lochmann, L.; Pospisil, J.; Lim, D. Tetrahedron Lett. 1966, 257.
12. Breed, L.W.; Elliott, R.L. Inorg. Chem. 1964, 3, 1622.
13. Wannagat, U.; Schreiner, G. Monatsh. Chem. 1965, 96, 1916.
14. Rochow, E.G.; Lienhard, K. Z. Anorgan Allg. Chem. 1964, 331, 316.
15. Wiseman, G.H.; Seyferth, D.; Wheeler, D.R. Organometallics 1986, 5, 146.

TABLE 1. Stoichiometric Ring Opening of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub> and (cyclo-Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub> by Organoalkali Reagents.

I. Reactions of cyclo-(Me<sub>2</sub>SiNMe)<sub>2</sub>

| Chlorosilane              |                                   |                                                                        |
|---------------------------|-----------------------------------|------------------------------------------------------------------------|
| <u>RLi</u>                | <u>Quench</u>                     | <u>Product (% Yield)</u>                                               |
| MeLi                      | Me <sub>3</sub> SiCl              | Me <sub>3</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>3</sub> (70)       |
| MeLi                      | Me <sub>2</sub> HSiCl             | Me <sub>3</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>2</sub> H (83)     |
| MeLi                      | Me <sub>2</sub> SiCl <sub>2</sub> | Me <sub>3</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>2</sub> Cl (57)    |
| n-BuLi                    | Me <sub>3</sub> SiCl              | n-BuMe <sub>2</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>3</sub> (81)   |
| n-BuLi                    | Me <sub>2</sub> HSiCl             | n-BuMe <sub>2</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>2</sub> H (86) |
| t-BuLi                    | Me <sub>3</sub> SiCl              | t-BuMe <sub>2</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>3</sub> (87)   |
| t-BuLi                    | Me <sub>2</sub> HSiCl             | t-BuMe <sub>2</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>2</sub> H (80) |
| MeLi/Me <sub>3</sub> CONa | Me <sub>3</sub> SiCl              | Me <sub>3</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>3</sub> (70)       |
| MeLi/Me <sub>3</sub> CONa | Me <sub>2</sub> ViSiCl            | Me <sub>3</sub> SiNMeSiMe <sub>2</sub> NMeSiMeVi (60)                  |
| MeLi/Me <sub>3</sub> COK  | Me <sub>3</sub> SiCl              | Me <sub>3</sub> SiNMeSiMe <sub>2</sub> NMeSiMe <sub>3</sub> (60)       |

II. Reactions of cyclo-(Me<sub>2</sub>SiNPr<sup>i</sup>)<sub>2</sub>

|        |                       |                                                                                                    |
|--------|-----------------------|----------------------------------------------------------------------------------------------------|
| MeLi   | Me <sub>2</sub> HSiCl | Me <sub>3</sub> SiNPr <sup>i</sup> SiMe <sub>2</sub> NPr <sup>i</sup> SiMe <sub>2</sub> H (64)     |
| n-BuLi | Me <sub>2</sub> HSiCl | n-BuMe <sub>2</sub> SiNPr <sup>i</sup> SiMe <sub>2</sub> NPr <sup>i</sup> SiMe <sub>2</sub> H (67) |

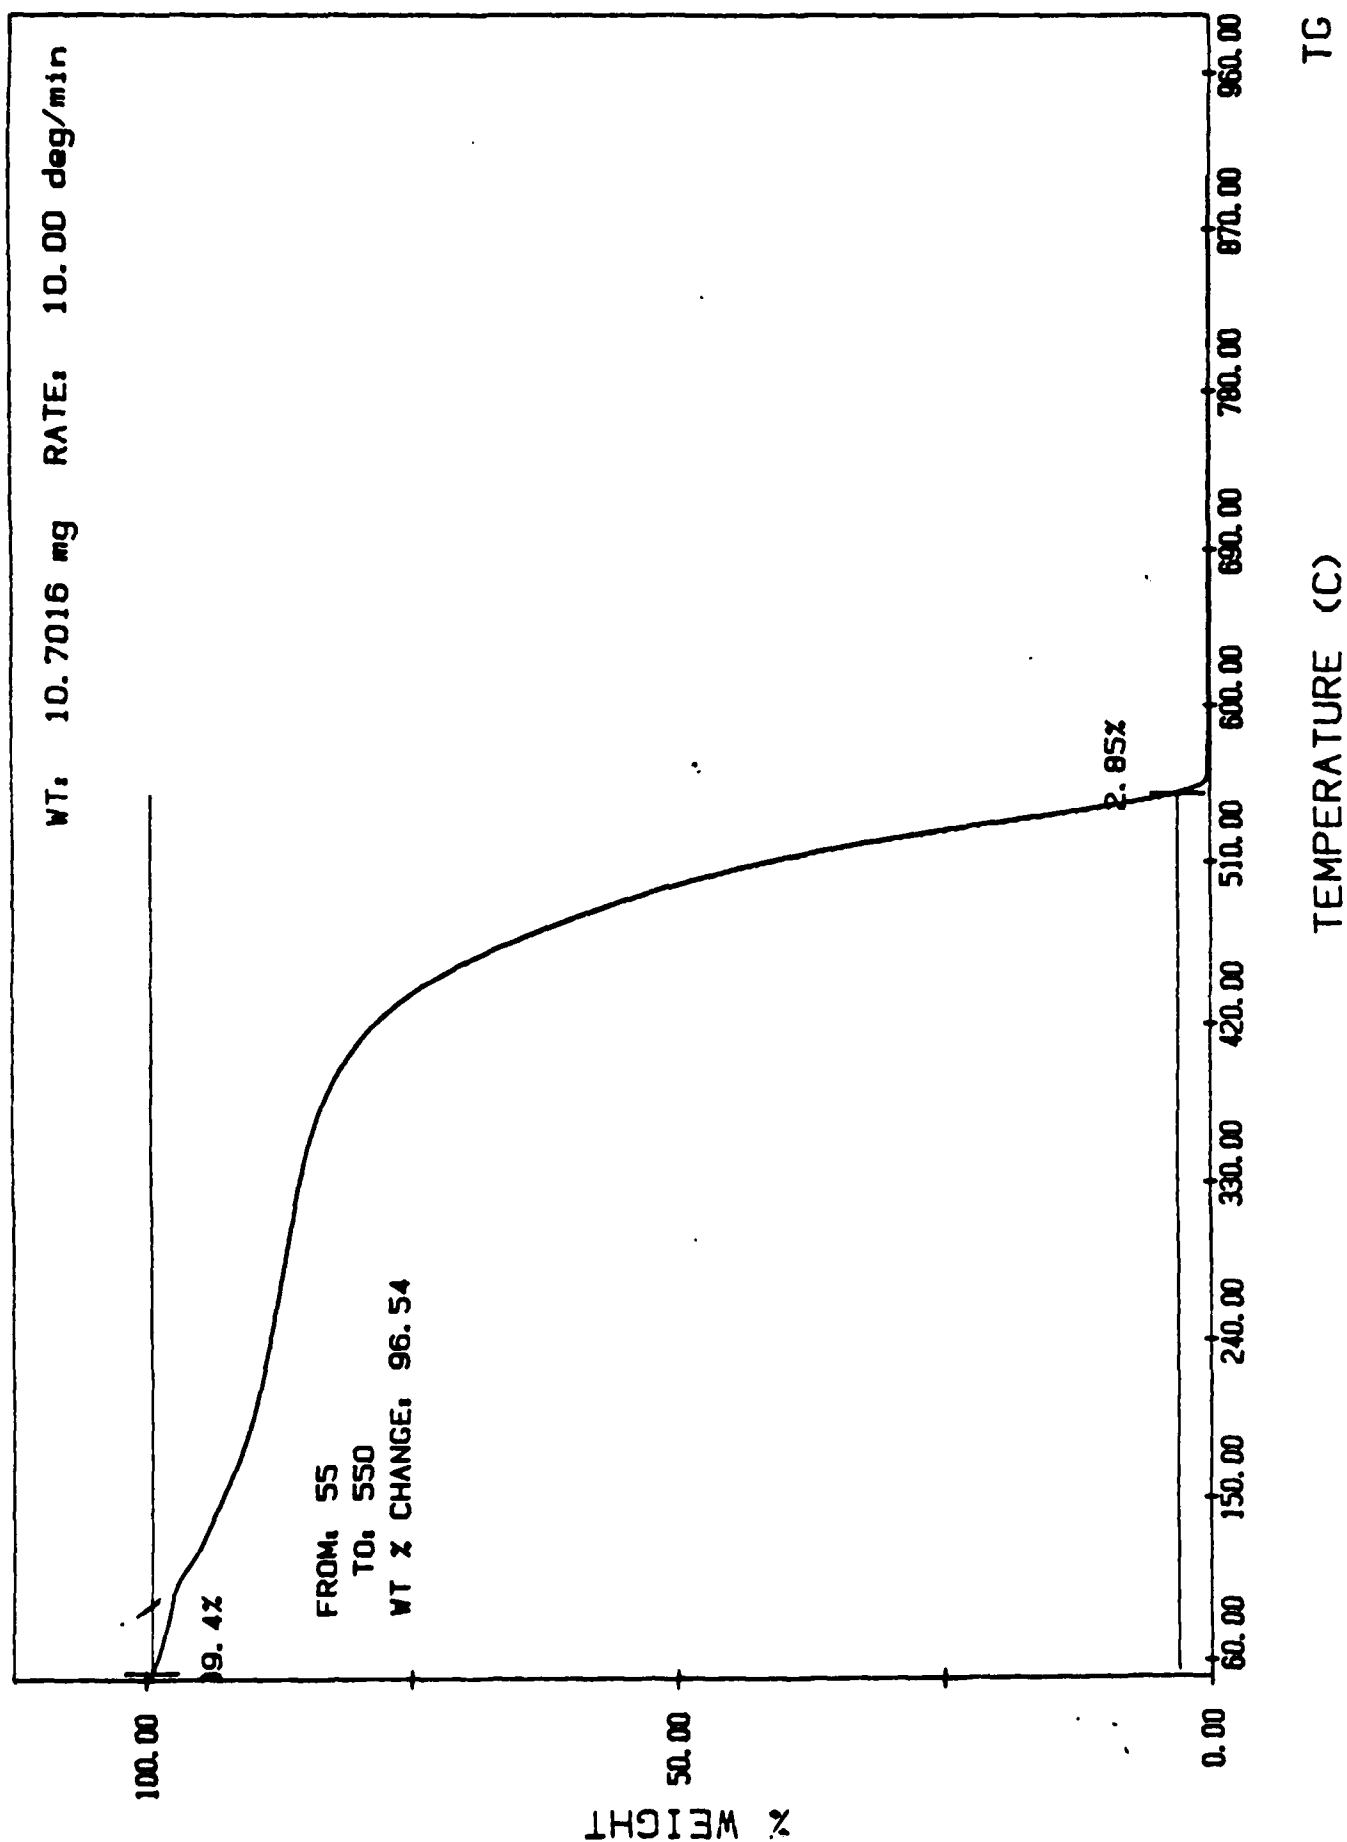


Fig. 1

TECHNICAL REPORT DISTRIBUTION LIST, GENERAL

|                                                                                                                  | <u>No.<br/>Copies</u>        |                                                                                                                                              | <u>No.<br/>Copies</u> |
|------------------------------------------------------------------------------------------------------------------|------------------------------|----------------------------------------------------------------------------------------------------------------------------------------------|-----------------------|
| Office of Naval Research<br>Chemistry Division, Code 1113<br>800 North Quincy Street<br>Arlington, VA 22217-5000 | 3                            | Dr. Ronald L. Atkins<br>Chemistry Division (Code 385)<br>Naval Weapons Center<br>China Lake, CA 93555-6001                                   | 1                     |
| Commanding Officer<br>Naval Weapons Support Center<br>Attn: Dr. Bernard E. Douda<br>Crane, IN 47522-5050         | 1                            | Chief of Naval Research<br>Special Assistant<br>for Marine Corps Matters<br>Code OOMC<br>800 North Quincy Street<br>Arlington, VA 22217-5000 | 1                     |
| Dr. Richard W. Drisko<br>Naval Civil Engineering Laboratory<br>Code L52<br>Port Hueneme, California 93043        | 1                            | Dr. Bernadette Eichinger<br>Naval Ship Systems<br>Engineering Station<br>Code 053<br>Philadelphia Naval Base<br>Philadelphia, PA 19112       | 1                     |
| Defense Technical Information Center<br>Building 5, Cameron Station<br>Alexandria, Virginia 22314                | 2<br><u>high<br/>quality</u> | Dr. Sachio Yamamoto<br>Naval Ocean Systems Center<br>Code 52<br>San Diego, CA 92152-5000                                                     | 1                     |
| David Taylor Research Center<br>Dr. Eugene C. Fischer<br>Annapolis, MD 21402-5067                                | 1                            | David Taylor Research Center<br>Dr. Harold H. Singerman<br>Annapolis, MD 21402-5067<br>ATTN: Code 283                                        | 1                     |
| Dr. James S. Murday<br>Chemistry Division, Code 6100<br>Naval Research Laboratory<br>Washington, D.C. 20375-5000 | 1                            |                                                                                                                                              |                       |

POLYMER PROGRAM DISTRIBUTION LIST

Dr. J. M. Augl  
Naval Surface Weapons Center  
White Oak, MD 20910

Dr. A. S. Abhiraman  
School of Chemical Engineering  
Georgia Institute of Technology  
Atlanta, GA 30332

4132033

Dr. Harry R. Allcock  
Department of Chemistry  
Pennsylvania State University  
University Park, PA 16802

Dr. Chris W. Allen  
Department of Chemistry  
University of Vermont  
Burlington, VT 05405

4132007

413c012

Dr. Ronald D. Archer  
Department of Chemistry  
University of Massachusetts  
Amherst, MA 01003

Dr. Ali S. Argon  
Mechanical Engineering Department  
Massachusetts Institute of Technology  
Cambridge, MA 02139

413c028

a400005df

Dr. William J. Bailey  
Department of Chemistry  
University of Maryland  
College Park, MD 20742

Dr. Kurt Baum  
Fluorochem, Inc.  
680 S. Ayon Avenue  
Azusa, CA 91702

413a006

4000021sbl

Dr. Frank D. Blum  
Department of Chemistry  
University of Missouri - Rolla  
Rolla, MO 65401

Dr. Len J. Buckley  
Naval Air Development Center  
Code 6063  
Warminster, PA 18974

413m005

Dr. F. James Boerio  
Materials Science & Engineering Dept.  
University of Cincinnati  
Cincinnati, Ohio 45221

Dr. Ivan Caplan  
DTNSRDC Annapolis  
Code 0125  
Annapolis, MD 21401

413m012

Dr. Robert E. Cohen  
Department of Chemical Engineering  
Massachusetts Institute of Technology  
Cambridge, MA 02139

4132001

Dr. E. Fischer  
DTNSRDC Code 2853  
Annapolis, MD 21402

Dr. Curtis W. Frank  
Department of Chemical Engineering  
Stanford University  
Stanford, CA 94305

413h005

Dr. Gregory S. Girolami  
School of Chemical Sciences  
University of Illinois  
Urbana-Champaign, IL 61801

4132014

Dr. Robert H. Grubbs  
Department of Chemistry  
California Institute of Technology  
Pasadena, CA 91124

4132019

Dr. James F. Haw  
Department of Chemistry  
Texas A&M University  
College Station, TX 77843

413c039

Dr. Stuart L. Cooper  
Department of Chemical Engineering  
University of Wisconsin  
Madison, WI 53706

4132006

Dr. Warren T. Ford  
Department of Chemistry  
Oklahoma State University  
Stillwater, OK 74078

413h006

Dr. John K. Gillham  
Department of Chemical Engineering  
Princeton University  
Princeton, New Jersey 08544

413c005

Dr. Bernard Gordon  
Department of Polymer Science  
Pennsylvania State University  
University Park, PA 16802

413c025

Dr. Henry K. Hall  
Department of Chemistry  
University of Arizona  
Tucson, AZ 85721

413j009

Dr. Alan J. Heeger  
Department of Physics  
University of California, Santa Barbara  
Santa Barbara, CA 93106

4132012

Dr. Pat J. Hendra  
Department of Chemistry  
University of Southampton  
Highfield Southampton 509 5NH  
United Kingdom  
4134001

Dr. Bruce S. Hudson  
Department of Chemistry  
University of Oregon  
Eugene, Oregon 97403

413c018

Dr. Hatsuo Ishida  
Department of Macromolecular Science  
Case Western Reserve University  
Cleveland, OH 44106

413m008

Dr. Paul M. Lahti  
Department of Chemistry  
University of Massachusetts  
Amherst, MA 01003

413c037

Dr. Robert W. Lenz  
Polymer Science and Engineering Dept.  
University of Massachusetts  
Amherst, MA 01002

441c013

Dr. Alan <sup>Cz</sup> MacDiarmid  
Department of Chemistry  
University of Pennsylvania  
Philadelphia, PA 19104

a400004df

Dr. Charles E. Hoyle  
Department of Polymer Science  
University of Southern Mississippi  
Hattiesburg, MS 39406-0076

413c026

Dr. Leonard V. Interrante  
Department of Chemistry  
Rensselaer Polytechnic Institute  
Troy, NY 12181

413c014

Dr. Jeffrey T. Koberstein  
Institute of Materials Science  
University of Connecticut  
Storrs, CT 06268

4132013

Dr. Richard M. Laine  
Washington Technology Center  
University of Washington  
Seattle, WA 98195

s400033srh

Dr. Geoffrey Lindsay  
Chemistry Division - Code 087  
Naval Weapons Center  
China Lake, CA 93555

4132036

Dr. Chris W. Macosko  
Materials Science & Engineering Dept.  
University of Minnesota  
Minneapolis, MN 55455

4132029

Dr. Joseph H. Magill  
Materials Science & Engineering Dept.  
University of Pittsburgh  
Pittsburgh, PA 15161

413c013

Dr. Tobin J. Marks  
Department of Chemistry  
Northwestern University  
Evanston, IL 60201

413c030

Dr. Krzysztof Matyjaszewski  
Department of Chemistry  
Carnegie Mellon University  
Pittsburgh, PA 15213

413j002

Dr. William B. Moniz  
Code 6120  
Naval Research Laboratory  
Washington, DC 20375-5000

4132012

Dr. Virgil Percec  
Department of Macromolecular Science  
Case Western Reserve University  
Cleveland, OH 44106-2699

413c024

Dr. Roger S. Porter  
Dept. of Polymer Science & Engineering  
University of Massachusetts  
Amherst, MA 01002

413m006

Dr. Leo Mandelkern  
Department of Chemistry  
Florida State University  
Tallahassee, FL 32306-3015

4132018

Dr. Lon J. Mathias  
Department of Polymer Science  
University of Southern Mississippi  
Hattiesburg, MS 30406-0076

413m003

Dr. James E. McGrath  
Department of Chemistry  
Virginia Polytechnic Institute  
Blacksburg, VA 24061

4132007

Dr. Kay L. Paciorek  
Ultrasystems Defense and Space, Inc.  
16775 Von Karman Avenue  
Irvine, CA 92714

s400029srh

Dr. Martin Pomerantz  
Department of Chemistry  
University of Texas at Arlington  
Box 19065  
Arlington, TX 76019-0065  
a400008df

Dr. T. J. Reinhart, Jr.  
Nonmetallic Materials Division  
Air Force Materials Laboratory (AFSC)  
Wright-Patterson AFB, OH 45433

Dr. Arnost Reiser  
Institute of Imaging Sciences  
Polytechnic University  
333 Jay Street  
Brooklyn, NY 11021

4132022

Dr. Charles M. Roland  
Code 6120  
Naval Research Laboratory  
Washington, DC 20375-5000

413m009

Dr. Ronald Salovey  
Department of Chemical Engineering  
University of Southern California  
Los Angeles, CA 90089

413m010

Dr. Jerry I. Scheinbeim  
Dept. of Mechanics & Materials Science  
Rutgers University  
Piscataway, NJ 08854

4132009

Dr. L. E. Slotter  
Code Air 931-A  
Naval Air Systems Command  
Washington, D. C. 20361-9310

Dr. Dietmar Seyferth  
Department of Chemistry  
Massachusetts Institute of Technology  
Cambridge, MA 02139

413c004

Dr. Ferdinand Rodriguez  
Department of Chemical Engineering  
Cornell University  
Ithaca, NY 14853

413c011

Dr. Michael F. Rubner  
Materials Science & Engineering Dept.  
Massachusetts Institute of Technology  
Cambridge, MA 02139

413m007

Dr. Jacob Schaefer  
Department of Chemistry  
Washington University  
St. Louis, MO 63130

413m001

Dr. Lawrence R. Sita  
Department of Chemistry  
Carnegie Mellon University  
Pittsburgh, PA 15213

4132030

Dr. Richard R. Schrock  
Department of Chemistry  
Massachusetts Institute of Technology  
Cambridge, MA 02139

4132038

Dr. David S. Soane  
Department of Chemical Engineering  
University of California, Berkeley  
Berkeley, CA 94720-9989

413h004

Dr. Les H. Sperling  
Materials Research Center #32  
Lehigh University  
Bethlehem, PA 18015

413c002

Dr. C. S. Sung  
Institute of Materials Science  
University of Connecticut  
Storrs, CT 06268

413m011

Dr. C. H. Wang  
Department of Chemistry  
University of Utah  
Salt Lake City, Utah 84112

413c020

Dr. Robert A. Weiss  
Department of Chemical Engineering  
University of Connecticut  
Storrs, CT 06268

a400006df

Dr. Garth L. Wilkes  
Department of Chemical Engineering  
Virginia Polytechnic Institute  
Blacksburg, VA 24061

4132020

Dr. Richard S. Stein  
Polymer Research Institute  
University of Massachusetts  
Amherst, MA 01002

4132008

Dr. Sukant K. Tripathy  
Department of Chemistry  
University of Lowell  
Lowell, MA 01854

4132016

Dr. Kenneth B. Wagener  
Department of Chemistry  
University of Florida  
Gainesville, FL 32611

a400007df

Dr. George M. Whitesides  
Department of Chemistry  
Harvard University  
Cambridge, MA 02138

4132010