

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

2

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

AD-A212 117

1a REPORT SECURITY CLASSIFICATION Unclassified			1b RESTRICTIVE MARKINGS DTIC FILE COPY	
2a SECURITY CLASSIFICATION AUTHORITY			3 DISTRIBUTION AVAILABILITY STATEMENT THIS DOCUMENT IS AVAILABLE TO THE PUBLIC WITHOUT LIMITATION AND IS NOT SUBJECT TO RESTRICTIONS ON DISTRIBUTION OR USE.	
2b DECLASSIFICATION/DOWNGRADING SCHEDULE				
4 PERFORMING ORGANIZATION REPORT NUMBER(S)			5 MONITORING ORGANIZATION REPORT NUMBER(S)	
6a NAME OF PERFORMING ORGANIZATION Dept. of Chemistry Cornell University		6b OFFICE SYMBOL (If applicable)		7a NAME OF MONITORING ORGANIZATION Office of Naval Research
6c ADDRESS (City, State, and ZIP Code) Dept. of Chemistry Cornell University Ithaca, NY 14853		7b ADDRESS (City, State, and ZIP Code) Chemistry Program 800 N. Quincy Street Alexandria, VA 22217		
8a NAME OF FUNDING SPONSORING ORGANIZATION Office of Naval Research		8b OFFICE SYMBOL (If applicable)		9 PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER
8c ADDRESS (City, State, and ZIP Code) Chemistry Program 800 N. Quincy St. Alexandria, VA 22217		10 SOURCE OF FUNDING NUMBERS		
		PROGRAM ELEMENT NO	PROJECT NO	TASK NO WORK UNIT ACCESSION NO
11 TITLE (Include Security Classification) Synthesis and Properties of NdNiO₃ Prepared by Low Temperature Methods				
12 PERSONAL AUTHOR(S) John K. Vassiliou, Marc Hornbostel, Robin P. Ziebarth, and Francis J. DiSalvo				
13a TYPE OF REPORT Technical Report		13b TIME COVERED FROM _____ TO _____		14 DATE OF REPORT (Year, Month, Day) 1989-8-16
15 PAGE COUNT				
16 SUPPLEMENTARY NOTATION				
17 COSATI CODES			18 SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	Oxide Conductors, Structural Phase Transitions Perovskites	
19 ABSTRACT (Continue on reverse if necessary and identify by block number) NdNiO₃ has been prepared with a rhombohedral perovskite structure by low temperature methods, and its magnetic and electric properties have been studied between 4 K and 300 K. The temperature coefficient of the resistivity changes at 130 K from positive (i.e. metal-like) to negative (i.e. semiconductor-like), with some thermal hysteresis at this "transition". The magnetic susceptibility shows Curie-Weiss behavior, modified by the changing thermal occupation of the Nd³⁺ crystal field levels, over the whole temperature range. Differential thermal analysis and thermogravimetric analysis showed oxygen loss beginning at 900°C in an N₂ atmosphere. Subsequent x-ray analysis at room temperature showed the presence of Nd₂NiO₄ and NiO. The electrical resistivity of sintered polycrystalline samples (1.5 x 10⁻² ohm-cm at 300K) is somewhat above the expected minimum metallic conductivity, but the observation of a positive constant term in the susceptibility above 100K suggests metallic band behavior. The hysteresis near 130K suggests a structural distortion at low temperatures.				
20 DISTRIBUTION AVAILABILITY OF ABSTRACT ☒ UNCLASSIFIED/UNLIMITED ☒ SAME AS RPT ☐ DTIC USERS			21 ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a NAME OF RESPONSIBLE INDIVIDUAL Dr. Mark Roff			22b TELEPHONE (Include Area Code) 202-696-4409	22c OFFICE SYMBOL

DTIC
ELECTE
SEP 11 1989
S E

65

43

OFFICE OF NAVAL RESEARCH

Grant or Contract N00014-88-K-0139

R&T Code 4131035

Technical Report No. 1

Synthesis and Properties of NdNiO_3
Prepared by Low Temperature Methods

by

John K. Vassiliou, Marc Hornbostel,
Robin P. Ziebarth, and Francis J. DiSalvo

Prepared for Publication

in the

Journal of Solid State Chemistry

Cornell University
Department of Chemistry
Ithaca, NY 14853

August 16, 1989

Reproduction in whole or in part is permitted for any purpose
of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited

SYNTHESIS AND PROPERTIES OF NdNiO_3 PREPARED
BY LOW TEMPERATURE METHODS

John.K. Vassiliou, Marc Hornbostel,
Robin Ziebarth and F.J. DiSalvo*

Department of Chemistry, Cornell University, Ithaca, N.Y 14853

ABSTRACT

NdNiO_3 has been prepared with a rhombohedral perovskite structure by low temperature methods, and its magnetic and electric properties have been studied between 4 K and 300 K. The temperature coefficient of the resistivity changes at 130 K from positive (i.e. metal-like) to negative (i.e. semiconductor-like), with some thermal hysteresis at this "transition". The magnetic susceptibility shows Curie-Weiss behavior, modified by the changing thermal occupation of the Nd^{+3} crystal field levels, over the whole temperature range. Differential thermal analysis and thermogravimetric analysis showed oxygen loss beginning at 900 C in an N_2 atmosphere. Subsequent xray analysis at room temperature showed the presence of Nd_2NiO_4 and NiO . The electrical resistivity of sintered polycrystalline samples (1.5×10^{-2} ohm-cm at 300 K) is somewhat above the expected minimum metallic conductivity, but the observation of a positive constant term in the susceptibility above 100 K suggests metallic band behavior. The hysteresis near 130 K suggests a structural distortion at low temperatures.

* author to whom correspondence should be addressed

Accession For	
NTIS GRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	



Introduction

Considerable interest in conducting oxides has been generated by the discovery of high temperature superconductivity in some copper oxide based compounds. Metallic conductivity is quite uncommon in oxides and only a few of those are in fact superconductors. Since the mechanism for high temperature superconductivity is as yet not agreed to, experimental studies of conducting oxides in general may help in our understanding of the necessary conditions for superconductivity and may result in further discoveries of new phenomena. Since the known metallic oxides occur mostly in compounds of the transition metals, we have initiated a study of such oxides. Here we report the properties of a new nickel oxide, NdNiO_3 .

In most nickel oxide compounds nickel is divalent; however, there are a few compounds where Ni adopts a higher oxidation state. These are mostly rare earth or alkaline earth ternary metal oxides. Among these compounds LaNiO_3 , a rhombohedrally distorted perovskite phase, is known to be a narrow band metallic conductor. Nickel compounds with Ni formal valency higher than two are usually unstable at high temperatures. Their synthesis, if possible, should therefore take place at low temperatures.

A number of authors(1,2,3) have reported the preparation of RNiO_3 compounds (R = rare earth element) involving high temperatures and atmospheric or high oxygen pressures. LaNiO_3 has been synthesized at 1 atm oxygen pressure and at 600C. The other rare earth compounds, isotypical to LaNiO_3 , have been synthesized at 950C and 60 Kbar pressure from mixtures of (R_2O_3) rare earth oxides, NiO , and KClO_3 . The decomposition of KClO_3 provided the necessary oxygen atmosphere. This reaction does not take place at atmospheric pressure and 950C; rather, R_2NiO_4 compounds with the K_2NiF_4 structure usually result (4). The electrical properties of these rare earth phases, with the exception of LaNiO_3 , have not been measured.

We report here the preparation of NdNiO_3 at 650 C and at atmospheric pressure using low temperature preparatory methods(5). The structure of NdNiO_3 is similar to the structure of perovskites with a rhombohedral distortion(2,6).

Methods of preparation

The samples were prepared by two methods: by decomposing well-mixed solid nitrates, and by a sol-gel precipitation decomposition process.

For the preparation involving solid nitrates, stoichiometric quantities of Nd_2O_3 and NiO of high purity were mixed together and dissolved in concentrated nitric acid. The excess nitric acid was removed by gentle heating. The remaining powder was slowly heated to 400 C for 1 hour. At that temperature the intimately mixed nitrates decomposed and the initially green powders turned

black. Pellets of this material were cold-pressed at 4 Kbar and heated to 650 C for 120 hours in an alumina crucible in oxygen atmosphere.

In the Sol-gel method, we started with aqueous solutions of the metal nitrates and a mixture of citric acid and ethylene glycol, in ratio of 10g of citric acid to 4ml of ethylene glycol and 4g of metal nitrates. The above ingredients were mixed together, and drops of HNO_3 were added to catalyze gel formation. The excess nitric acid was boiled off and the gel was decomposed by further heating to 400 C. The remaining black powder was cold pressed to 4 Kbar and heated to 650 C for 120 hours in an alumina crucible in an oxygen atmosphere.

The resulting ceramic materials, obtained by either of the above methods, are black single-phase materials with high electrical conductivity.

Other preparation methods were attempted, including reaction of well ground oxides and coprecipitation and rapid evaporation. However, sufficient mixing was apparently not achieved by either method and even after extended heating, multiphase products usually resulted.

Crystal structure

X-ray diffraction patterns were taken at room temperature using a Sintag XDS-2000 powder diffractometer and Cu-K α radiation. Si was used as an internal standard. The diffraction pattern of NdNiO_3 (Table I) is similar to the pattern of LaNiO_3 , suggesting that the crystal symmetry is rhombohedral R-3c (or hexagonal D_{3d}^6). The structure is a rhombohedrally distorted cubic perovskite. Since the tolerance factor, t , in the Goldsmith relation (7,8) is $t=0.85$, the rhombohedral distortion is expected. Note, however, that the structure and peak intensities are different from the orthorhombic cell reported for the phase prepared at high pressure (3).

The diffraction peaks are broad (e.g. 0.5 degrees FWHM at 47.5 degrees two theta) and the width increases with increasing two theta. Such broadening is consistent with small grain sizes of approximately 175 Å. These small sizes are likely a result of the low temperature preparation methods used to prepare the material. Other factors which could contribute to the broadening include small differences in stoichiometry across the sample, crystalline defects, and frozen in mechanical strains. This broadening makes an exact determination of the rhombohedral distortion difficult. Our best estimate for the rhombohedral angle is 60.5 ± 0.2 degrees. The dimensions of the resulting rhombohedral and its equivalent triple hexagonal unit cell are given in table I.


Since the rhombohedral angle of the primitive cell

($\alpha=60.5$) is close to 60.0 degrees (60 degrees is the rhombohedral angle of the primitive cell derived from a face centered cubic lattice), the x-ray pattern of NdNiO_3 can be approximately indexed in a cubic system. The unit cell length of the cubic pseudo-cell is $a = 3.85\text{\AA}$. The d-spacings and the observed intensities are also given in table I. The (hkl) indices were assigned on the basis of the rhombohedral and hexagonal cells.


Thermal analysis

Differential Thermal Analysis (DTA) and Thermogravimetric Analysis (TGA) were performed on the samples, using a Perkin-Elmer DTA-TGA thermal analysis system. The gas flow was 30 cc/min and the heating rate was 20 deg/min. Upon heating in an O_2 or N_2 atmosphere, an endothermic DTA peak appears, signaling the transformation of NdNiO_3 into a new phase. In a pure N_2 atmosphere, the onset temperature for the reaction is 900 C and the peak temperature is 960 C, while in a pure O_2 atmosphere the peak temperature has shifted to 1050 C.

Thermogravimetric Analysis in a N_2 atmosphere demonstrates that the above transformation is accompanied by oxygen loss. Upon heating, the recorded TGA pattern shows a rapid loss of oxygen, starting about 900 C, and achieving maximum rate of weight loss at 980C. After completion of the thermal cycle, the products of the reaction were examined by X-ray analysis. The X-ray powder pattern shows a mixed phase pattern, composed of NiO and Nd_2NiO_4 phases. Nd_2NiO_4 has tetragonal symmetry with the K_2NiF_4 structure(4). The reaction that takes place is:



At higher temperatures, in analogy with La_2NiO_4 (9), it is expected that Nd_2NiO_4 will decompose to the constituent oxides according to the reaction:



However, DTA experiments up to 1300 C did not show any sign of further decomposition.

Resistance measurements

The resistance of the samples was measured by the four probe method. Rectangular samples, cut from a pellet sintered at 650C in O_2 , were used for the electrical resistance measurements. The sample dimensions were roughly 10mmx2mmx2mm. Four wires were bonded to the samples by conducting silver paint and baked at 100C for 2 hours. The resistance of the contacts was less than the sample resistance, and their ohmic behavior was confirmed by testing the linearity of the current-voltage characteristics. The

room temperature measured resistivity is 1.5×10^{-2} ohm-cm. Due to the size of the contacts this value has a rather large uncertainty of about 25%. The temperature dependence of the resistance is given in Fig.1. In the temperature range between 130 K and 300 K, the behavior is metallic-like. At lower temperatures the behavior changes smoothly to semiconducting-like, the resistivity increases rapidly with decreasing temperature. Upon heating, the temperature dependence of the resistance follows a similar thermal pattern but with a large and repeatable hysteresis. The hysteresis appears the same independent of the cooling or heating rate, over rates of 0.5 K/sec to 5 K/sec.

In polycrystalline materials, the grain boundaries and the coupling between the grains may affect the transport properties of the samples significantly. In order to examine the effect of the grain boundaries on the temperature dependence of the resistance, we measured the resistance of samples prepared under different pressure and temperature conditions. Pellets were annealed at 600 C in an oxygen atmosphere under uniaxial stress of approximately of 0.5 Kbar. The temperature dependence of the resistance of the samples prepared this way does not show any measurable change from that shown above. While this suggests that grain boundary effects do not dominate the measured electrical properties, only a single crystal measurement can be conclusive.

Magnetic measurements

The magnetic susceptibility of the sample was measured between 4.2 K and 300 K by the Faraday method, at a magnetic field strength of 10 Kgauss. The field gradients at different fields were calibrated by using $\text{HgCo}(\text{SCN})_4$ as a standard (16.44×10^{-6} emu/g at 293 K, reference 10). This calibration was checked using several pure metals. Our measured values and literature values are (all in units of 10^{-6} emu/g): Hg, measured = -0.165, literature = -0.167 (10); Ta, measured = 0.859, literature = 0.851 (10) and 0.849 (10). We take these differences to estimate our absolute accuracy and conservatively quote $\pm 2\%$ absolute error on the value of the obtained susceptibility. The relative precision with which changes in the susceptibility with temperature can be measured depends upon the sample size and its susceptibility, but in this case the precision is better than 0.1%.

The susceptibility, χ , of NdNiO_3 at room temperature was independent of the applied magnetic field from 2 to 15 kG. This indicates that no ferromagnetic impurities contaminated the sample (11). The results of the temperature dependent measurements are plotted in Fig. 2. The higher temperature data are better illustrated in a plot of the inverse susceptibility vs. temperature (fig. 3). At room temperature, the susceptibility is 2.25×10^{-5} emu/g, typical of a paramagnetic substance with a large concentration of local magnetic moments. At lower temperatures, the susceptibility increases, displaying

paramagnetic Curie-Weiss behavior.

In simple cases, the data might be expected to fit the Curie-Weiss equation:

$$X = C/(T+T_C) + X_0$$

where C and T_C are the Curie constant and Curie temperature respectively. X_0 is usually a constant which includes the Pauli-Landau paramagnetic susceptibility, the core diamagnetic susceptibility, and the Van Vleck susceptibility. However, in this case the Curie "constant" is temperature dependent due to crystal field splitting of the $J = 9/2$ ground state. To first order we might estimate the magnitude of the crystal field by comparison to other Nd oxides. The susceptibility of Nd_2O_3 shows a deviation from simple Curie-Weiss behavior below about 80 K (12) as the crystal field levels become thermally depopulated.

Since the crystal field energies will vary somewhat from compound to compound, we cannot be certain of the temperature interval for which the Curie-Weiss expression is a meaningful form with which to fit the data. On the other hand, if the temperature interval is too short, the data will be fit about equally well over some range of T_C and X_0 values, making a determination of these values with any confidence problematic. We fit the data over the intervals 80 to 300K, 100K to 300K, and 120 to 300K. The best fits varied somewhat depending upon the interval used, from $C = 6.53 \times 10^{-3}$ emu-K/g, $T_C = 32\text{K}$, and $X_0 = 2.48 \times 10^{-6}$ emu/g over the interval 80 to 300K, to $C = 7.24 \times 10^{-3}$ emu-K/g, $T_C = 44\text{K}$, and $X_0 = 1.02 \times 10^{-6}$ emu/g over 120K to 300K. We note that the T_C values do not reflect exchange interactions only, but also reflect the leading corrections to the susceptibility due to the crystal field splitting of the Nd levels. While we cannot obtain the values of the constants in the Curie-Weiss expression with a high degree of confidence due to the above fitting difficulties, it is clear that a positive X_0 of 1 to 3×10^{-6} is present. If the data are forced to fit an expression with $X_0 = 0.0$ or a $T_C = 0.0$, the goodness of fit to the Curie-Weiss expression over the above temperature intervals is a factor of 4 to 5 poorer (standard deviations increase from 0.2% to above 1%).

The magnetic moment per Nd obtained from the above fits to the Curie-Weiss law vary from 3.61 Bohr magnetons (80 K to 300 K fit) to 3.80 Bohr magnetons (120 to 300K fit). These values compare favorably with the theoretical moment expected for a free Nd^{+3} ion of 3.62 Bohr magnetons. If the material contained magnetic Ni^{+3} ions, they would contribute to the measured Curie constant as well. If we approximated that nickel moment as a $g = 2$ and $S = 1/2$ moment, then the minimum value of C we could obtain would be 8.04×10^{-3} emu-K/g, well above the range determined from the fit.

Discussion

Since the structure and nickel valence are the same as those of LaNiO_3 , and since the unit cell volume is a little smaller in NdNiO_3 than that of LaNiO_3 (the rhombohedral unit cell volumes are 112.6 and 112.9 $\text{\AA}^3$, respectively), a metallic band at the Fermi level is expected for NdNiO_3 . This band should be of Ni e_g parentage (13). The bandwidth is primarily determined by the strong O- e_g -O overlap of the oxygen orbitals and the d-orbitals of the Ni^{+3} ion in the slightly distorted octahedral field.

Between 300 K and 130 K the resistance decreases with decreasing temperature as expected for a metal. However, the room temperature resistivity of 1.5×10^{-2} ohm-cm is high for a metallic material. A similarly prepared sample of LaNiO_3 had a room temperature resistivity of 4×10^{-3} ohm-cm. The lowest reported literature value for the resistivity of LaNiO_3 samples sintered at high temperatures is about 1×10^{-3} ohm-cm. The minimum metallic conductivity (13,14) expected for the Nd compound, assuming one conduction electron per Ni, would be on the order of 10^{-3} ohm-cm, as it is for LaNiO_3 . It might be that the high value of the resistivity is due to the polycrystalline nature of the sample and the low sintering temperatures. Indeed, combined with the positive value of X_0 and the fact that the value of C is less than expected if Ni^{+3} also had a magnetic moment, it would appear that this compound is indeed a metal, but close to the metal-insulator boundary.

Below 130 K the resistivity increases with decreasing temperature. Fig. 4 shows a plot of $\ln R$ vs $1/T$. Between 130 K and 50 K the conductivity is thermally activated with an activation energy of 80 K. This behavior is typical of a semiconductor, indicating that NdNiO_3 undergoes a metal-semiconductor transition at about 130 K. Below 10 K the data is fit by a much lower activation energy, 5 K. This lower activation energy might be expected for a semiconductor as it changes from intrinsic to extrinsic behavior as the temperature is lowered. It is likely that this "transition" near 130 K is structural in nature, since an obvious hysteresis is seen in the resistivity. Essentially no anomaly is seen in the susceptibility, although the large contribution of the local moment paramagnetism may mask small temperature dependent changes in X_0 that should result from a metal-insulator transition. It is perhaps coincidental that the deviation of the inverse susceptibility from straight line behavior in fig. 3 also occurs near 130 K, although in a very gradual manner. This possible temperature dependence in X_0 would also cause difficulty in trying to fit the data to the Curie-Weiss susceptibility, although at 130K X_0 is perhaps only 2 to 5% of the total susceptibility.

A variety of interpretations can be given to the above data. These would include a Mott transition at 130 K or small polaron formation at that same temperature. It is even possible that a transition is driven by the small interaction of the conduction

electrons in an almost localized band with the Nd magnetic moments.

A model consistent with the resistivity measurements is based on a Mott-Hubbard metal-insulator transition. The narrow d band of NdNiO₃ is half filled, and at room temperature the conductivity is metallic. We can assume that at 130 K NdNiO₃ undergoes an antiferromagnetic transition as in the case of LaTiO₃ (15). The half filled band is split into an upper empty band and a lower completely filled band. The energy gap developing from the splitting of the Hubbard bands is responsible for the semiconducting character of the resistivity. However, the changes in the susceptibility due to the antiferromagnetic ordering is masked by the strong paramagnetic signal due to the f-electrons of the Nd³⁺ ions.

Another mechanism able to explain the semiconducting behavior below 130 K is polaron formation (13). At room temperature, the conductivity of NdNiO₃ is above the value of the minimum metallic conductivity (14) of $10^{+3} \text{ (Ohm.cm)}^{-1}$. In this limit, the mean free path of the electrons is of the order of the interatomic distance. The electrons move in a diffusive way in the narrow d-bands whose width is determined by the uncertainty principle, $W = \hbar/t_s$, where W is the width of the band and t_s is the relaxation time. In the metallic regime between 300 K and 130 K the conductivity of NdNiO₃ is diffusive. Below 130 K, small polaron formation localizes the electrons and the conductivity behavior is semiconducting. In this temperature domain the relaxation time, t_s , is determined by the phonon-assisted hopping time of the electrons from site to site. The localization of the 3d electrons may be accompanied by a Jahn-Teller distortion, as in the case of LaMnO₃ (16). A large thermal hysteresis of this lattice distortion could be responsible for the large resistivity hysteresis observed.

With the present polycrystalline samples the resistivity data are not sufficiently convincing to allow detailed comparisons with any particular theory or to discriminate between them.

Summary

NdNiO₃ has been prepared in the same structure type as that of LaNiO₃ by a low temperature synthetic method, without the use of high oxygen pressures as previously used. The magnetic properties show qualitatively the expected behavior of Nd³⁺ in a crystal field. The electrical resistivity is metallic-like at room temperature, but it is about an order of magnitude higher than the expected minimum metallic conductivity. This may be due to the polycrystalline nature of the material. There is a "transition" to semiconductor-like behavior at about 130 K. Since this transition shows considerable thermal hysteresis, it appears to be a thermodynamically first order structural transition.

Since the lattice parameters of NdNiO_3 are slightly smaller than those of LaNiO_3 , the bandwidths are expected to be similar. Consequently NdNiO_3 might be expected to be a "normal" metal like LaNiO_3 . Further studies of NdNiO_3 , especially if single crystals can be prepared under pressure, are clearly needed to understand the puzzling behavior reported in this work.

Acknowledgements

We deeply appreciate the support of the Office of Naval Research. Support of RPZ through the NSF sponsored Materials Research Laboratory program at Cornell is also appreciated.

References

1. Gerard Demazeau, Alain Marbeuf, Michel Pouchard, and Paul Hagenmuller, *J.Solid State Chem.* 3, 582-589 (1971).
2. A.Wold, B.Post, E.Banks, *J. Amer. Chem. Soc.* 79, 4911 (1957).
3. A.Wold, R.J.Arnett, J.B.Goodenough, *J. Appl. Phys.* 29, 387 (1958).
4. B.Willer, M.Daire, *C.R.Acad. Sci.* 267, 1483 (1968).
5. M.Pechini, *U.S.P.* 3, 231 328/1966; M.Vallet-Regi, E.Garcia, and J.M.Gonzales-Calbert, *J. Chem. Soc. Dalton, Trans.* 775 (1988); H.Wang et al., *Inorg. Chem.* 26, 1476-1481 (1987); S.Davison, K. Smith, R. Kershaw, K. Dwight, and A. Wold, *Mat. Res. Bull.* 22, 1659-1664 (1987).
6. F.Bertaut, F.Forrat, *J.Phys.Radium* 17, 129 (1956); Megaw, *Darlington Acta Crystallogr.Sec.* A31, 161 (1975).
7. V.M.Goldschmidt, *Geochemische Verteilungsgesetze der Elemente VII,VIII* (1927/1928).
8. J.B.Goodenough, J.A.Kafalas, and J.M.Longo, "Preparation Methods in Solid State Chemistry", Edited by Paul Hagenmuller, Academic Press, 1972.
9. Hidehito Obayashi, Tetsuichi Kudo, *Japan. J. Appl. Phys.* 14 (1975).
10. $\text{HgCo}(\text{NCS})_4$: J. C. G. Bunzli, *Inorganica Chemica Acta*, 36, L413 (1979) and references therein. For the other standards see the Handbook of Chemistry and Physics CRC Press or Landolt-Bornstein series, vol 2, section 9, Magnetic Properties I Springer-Verlag (1962).
11. "Magnetochemistry" by P.W.Selwood, page 186, Interscience 2nd Edition (1956).
12. H.Hacker, M.S.Lin, and E.F.Westrum. *Proc. of IV conf. on Rear Earth Research.* Ed. LeRoy Eyring pub. Gordon and Breach (1965).
13. J.B.Goodenough, *Progress in Solid State Chemistry* 5, 145 (1971).
14. N.F.Mott, "Metal-Insulator Transitions", page 28, Taylor & Francis LTD, London (1974).
15. D.A.Maclean, J.E.Greedan, *Inorg.Chem.* 20, 1025-1029, (1981).

16. J.B.Goodenough, Mater.Res.Bull. 6, 967 (1971).

FIGURE CAPTIONS

- Figure 1 - Resistance versus temperature. The resistance shows a minimum near 120 K and thermal hysteresis at low temperatures.
- Figure 2 - Magnetic susceptibility versus temperature.
- Figure 3 - The inverse susceptibility versus temperature better shows the high temperature data.
- Figure 4 - The logarithm of the resistance versus inverse temperature is used to extract activation energies.

TABLE CAPTION

- Table I - The lattice parameters of NdNiO_3 for the rhombohedral and the equivalent hexagonal unit cell are given along with the appropriate miller indices and the observed peak intensity. Since the lines are broadened due to the small particle size, the line splittings due to the rhombohedral distortion are not directly observed. Rather the splitting is estimated from the excess width of multiple peaks over that estimated using the width calculated from the single (220) peak.


TABLE I


$(h\ k\ l)_{\text{rhom}}$	$(h\ k\ l)_{\text{hex}}$	$d(\text{obs})$	Relative Intensity
1 1 0	0 1 2	3.79	10
1 0 -1	1 1 0	2.72	100
2 1 1	1 0 4		
2 2 0	2 0 4	1.91	35
1 1 -2	3 0 0	1.567	25
2 -1 -1	2 1 4		
3 1 0	0 1 8		
3 2 0	2 1 5	1.465	5
3 3 1	2 0 7		
3 3 3	0 0 9		
2 0 -2	2 2 0	1.356	8
4 2 2	2 0 8		
3 2 -1	1 3 4	1.210	5
4 3 1	1 2 8		
4 0 0	4 0 4	1.100	8


hexagonal lattice parameters: $a = 5.44$ $c = 13.17$


rhombohedral parameters: $a = 5.40$ $\alpha = 60.5$ degrees

pseudo-cubic cell: $a = 3.85$

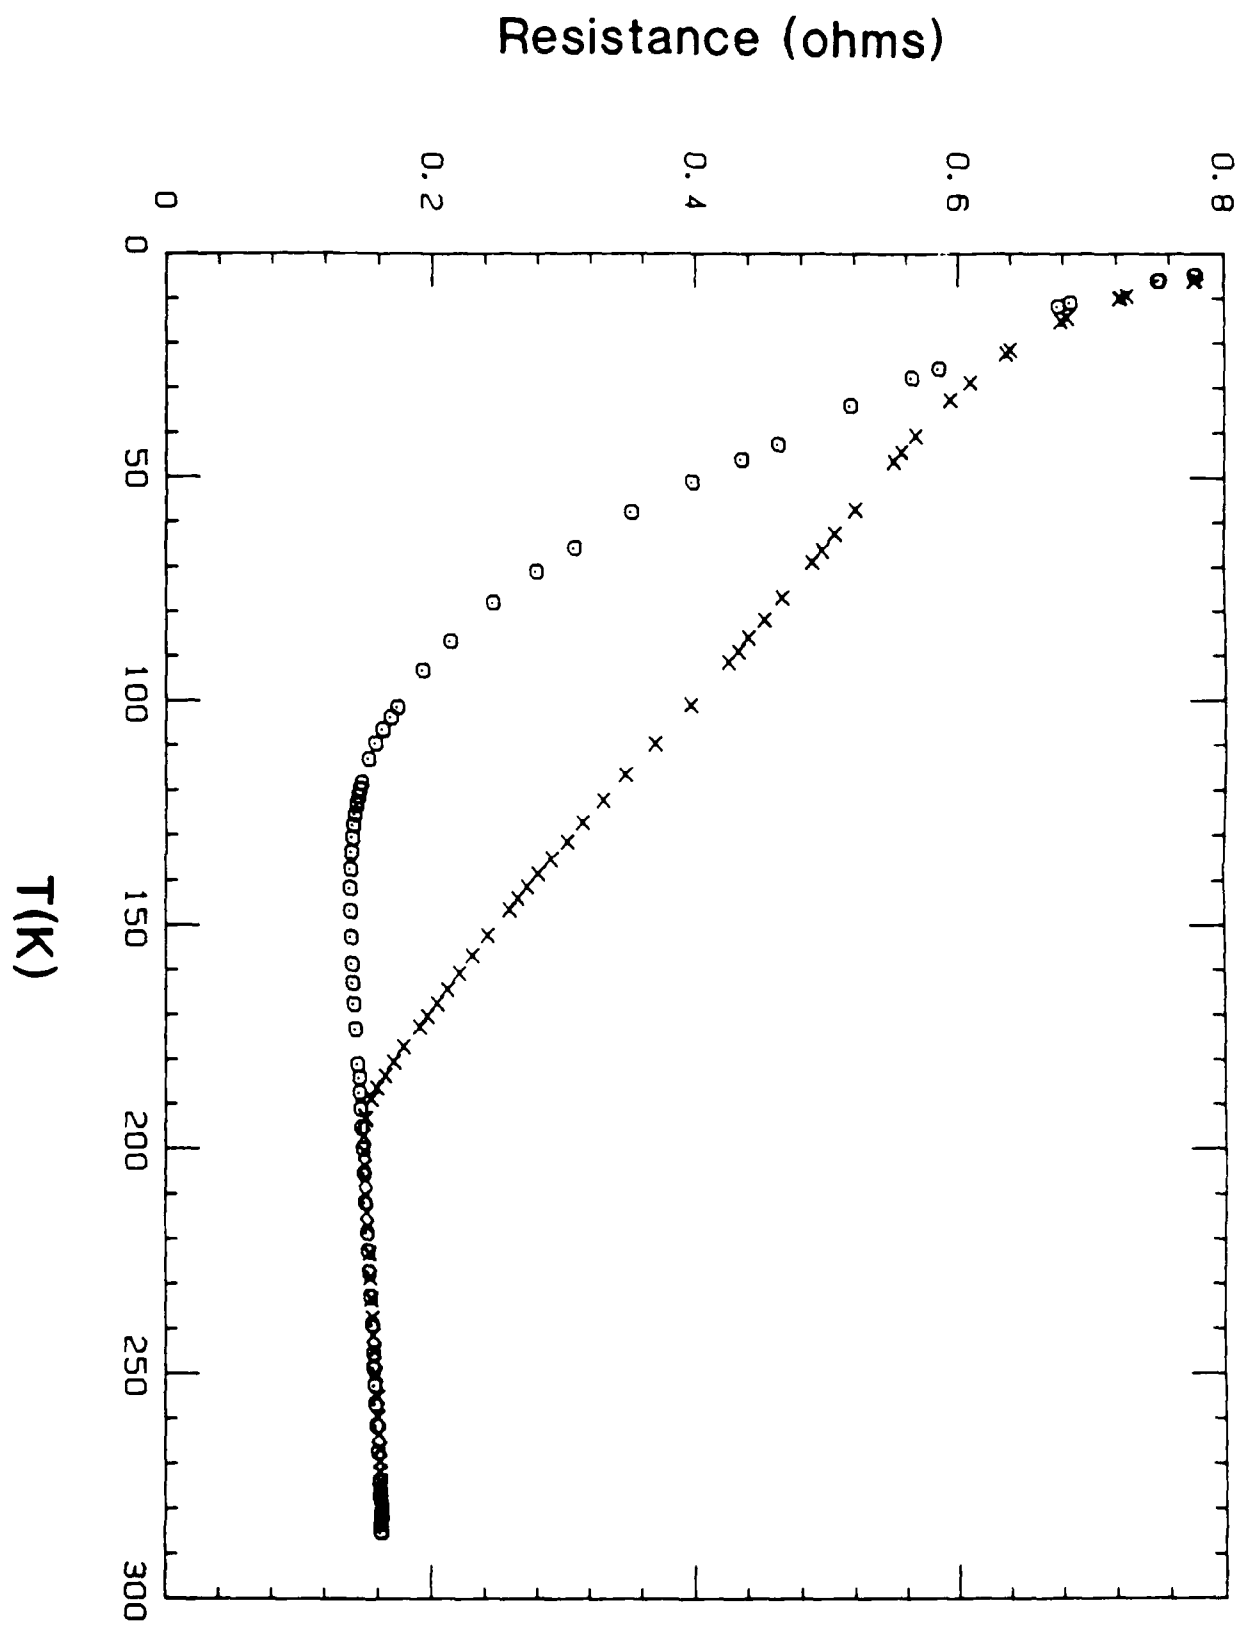

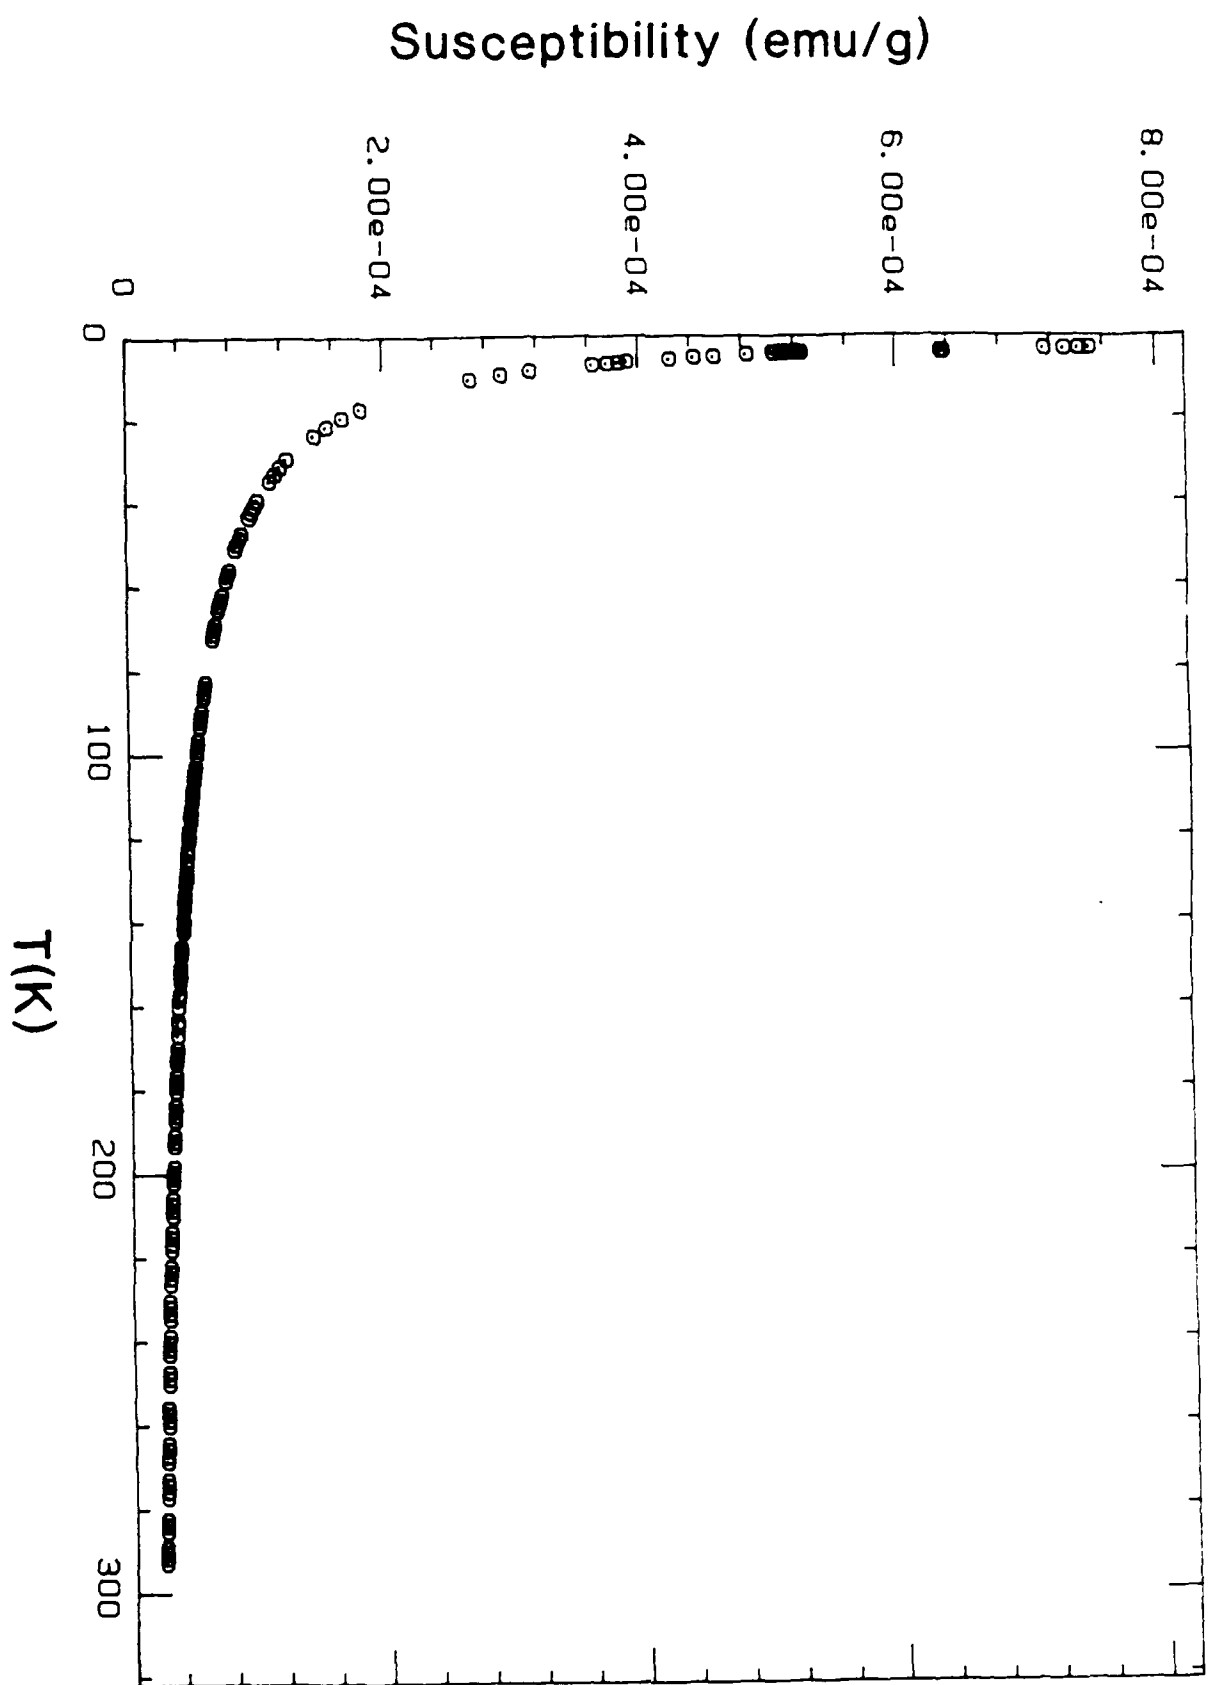

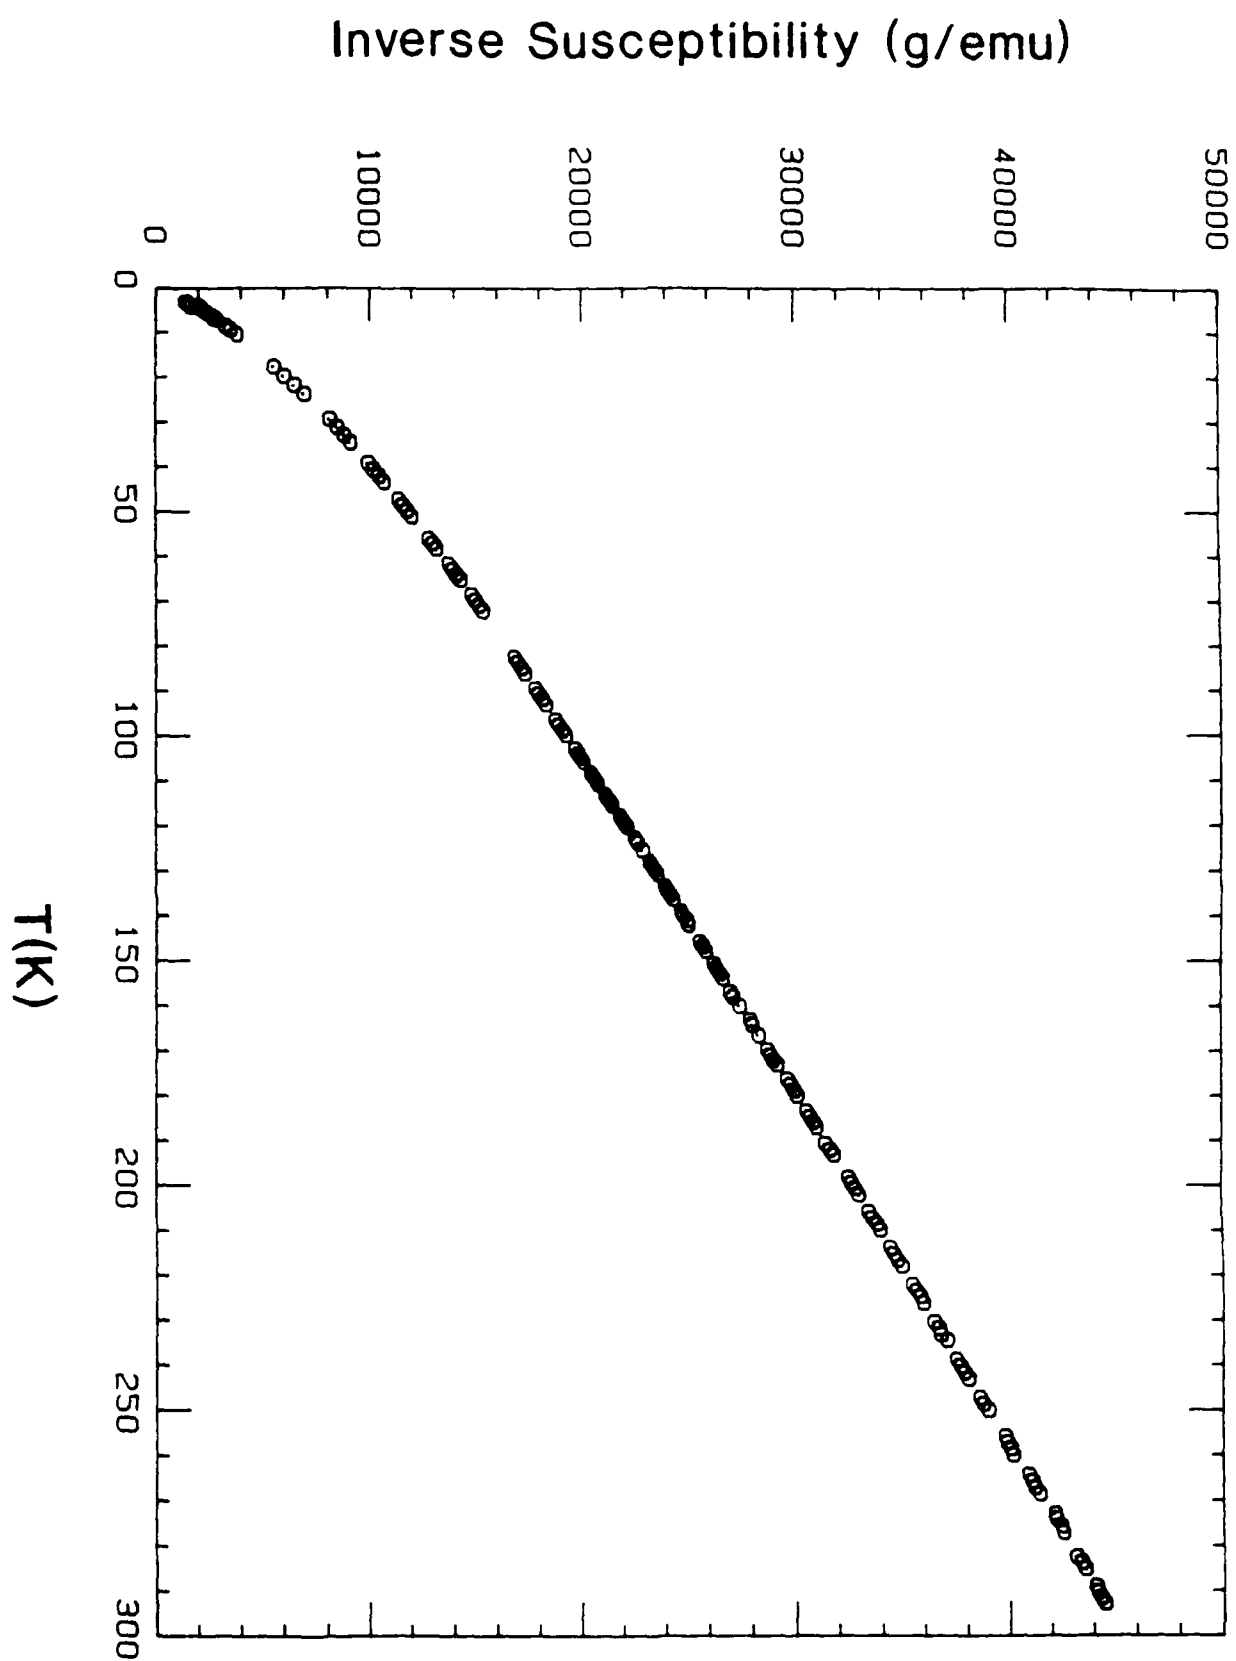

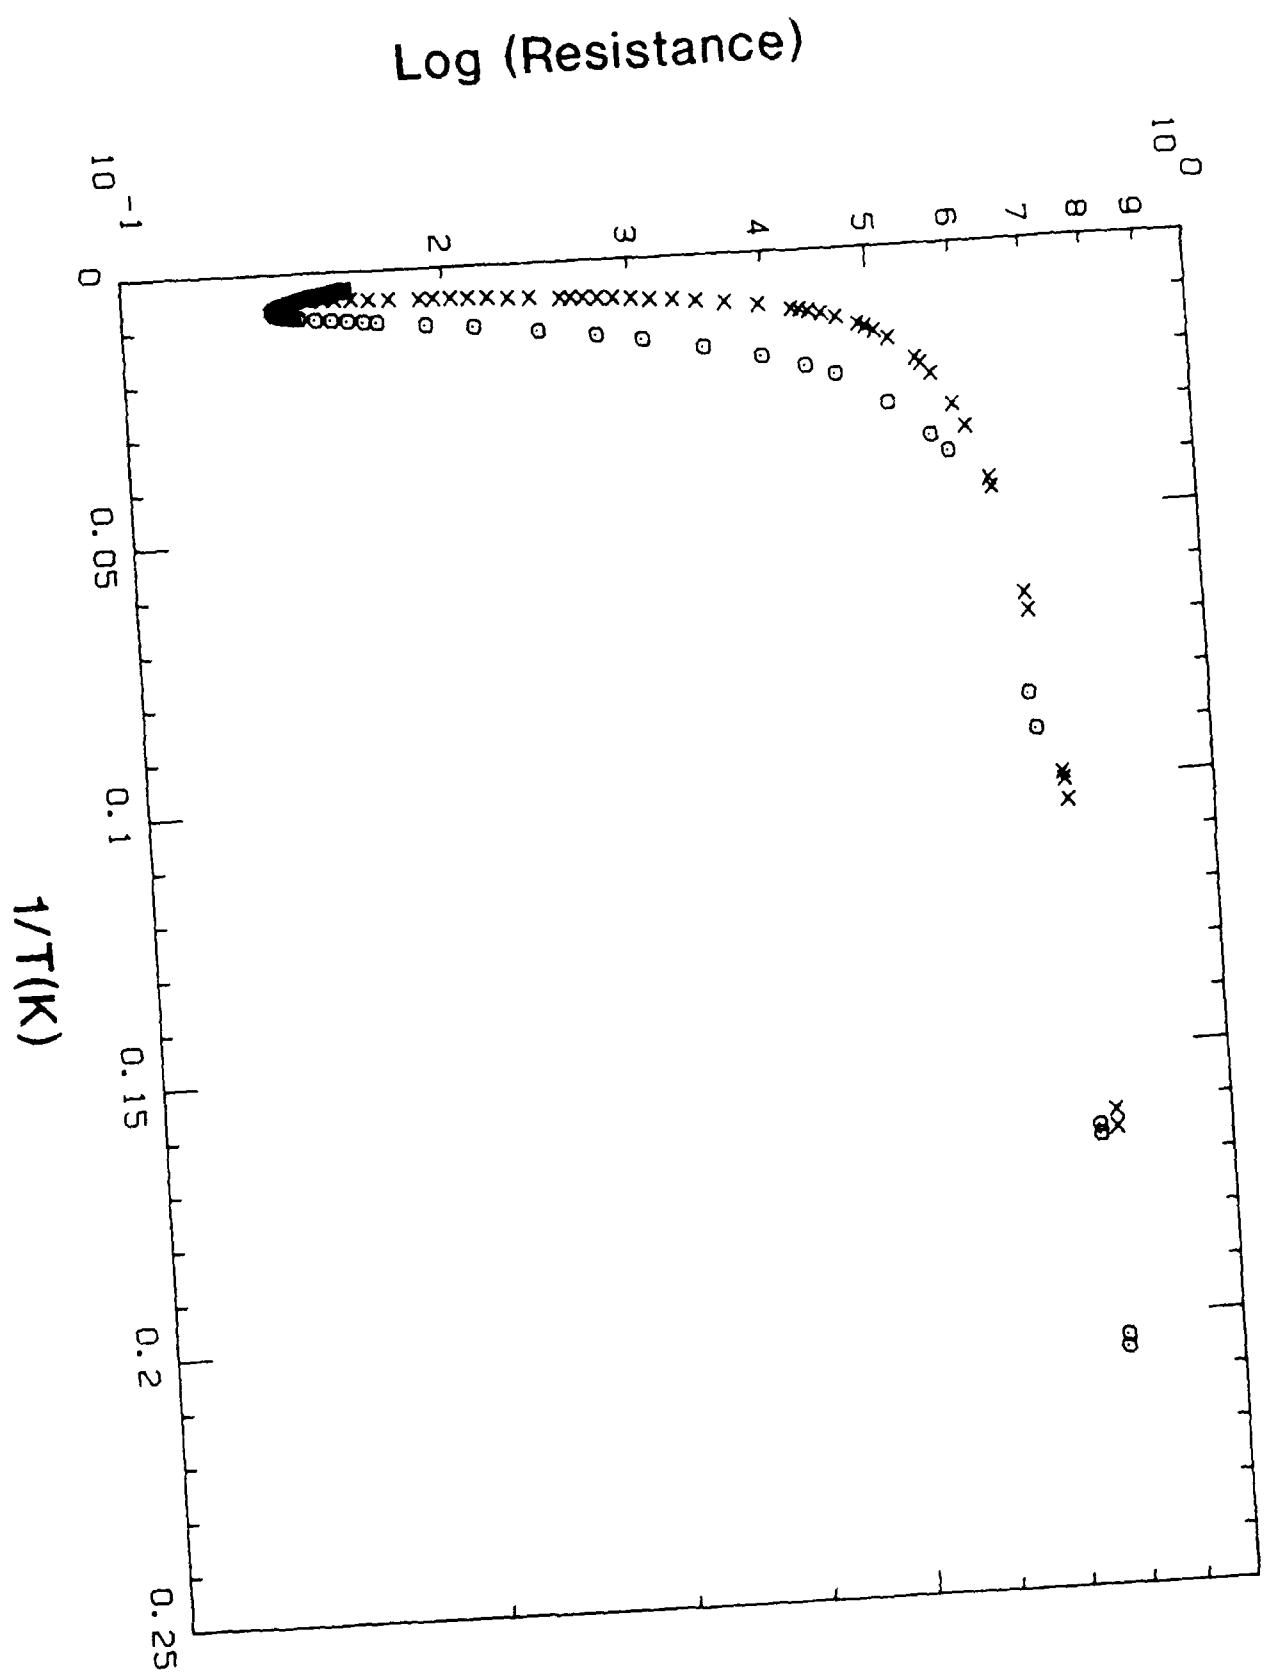

TECHNICAL REPORT DISTRIBUTION LIST, GENERAL

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Chemistry Division, Code 1113 800 North Quincy Street Arlington, VA 22217-5000	3	Dr. Ronald L. Atkins Chemistry Division (Code 385) Naval Weapons Center China Lake, CA 93555-6001	1
Commanding Officer Naval Weapons Support Center Attn: Dr. Bernard E. Douda Crane, IN 47522-5050	1	Chief of Naval Research Special Assistant for Marine Corps Matters Code 00MC 800 North Quincy Street Arlington, VA 22217-5000	1
Dr. Richard W. Drisko Naval Civil Engineering Laboratory Code L52 Port Hueneme, California 93043	1	Dr. Bernadette Eichinger Naval Ship Systems Engineering Station Code 053 Philadelphia Naval Base Philadelphia, PA 19112	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	2 <u>high</u> <u>quality</u>	Dr. Sachio Yamamoto Naval Ocean Systems Center Code 52 San Diego, CA 92152-5000	1
David Taylor Research Center Dr. Eugene C. Fischer Annapolis, MD 21402-5067	1	David Taylor Research Center Dr. Harold H. Singerman Annapolis, MD 21402-5067 ATTN: Code 283	1
Dr. James S. Murday Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1		