

2

DTIC FILE COPY



AD-A215 198

RESEARCH AND DEVELOPMENT TECHNICAL REPORT  
SLCET-TR-89-5

POLARIZATION MATRICES OF QUARTZ

ARTHUR BALLATO AND THEODORE LUKASZEK  
ELECTRONICS TECHNOLOGY AND DEVICES LABORATORY

JULY 1989

DISTRIBUTION STATEMENT

Approved for public release;  
distribution is unlimited.

DTIC  
ELECTE  
DEC 0 5 1989  
S DCS D

US ARMY  
LABORATORY COMMAND  
FORT MONMOUTH, NEW JERSEY 07703-5000

## NOTICES

### Disclaimers

The citation of trade names and names of manufacturers in this report is not to be construed as official Government indorsement or approval of commercial products or services referenced herein.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

Form Approved  
OMB No 0704-0188

## REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS		
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION / AVAILABILITY OF REPORT Approved for public release; distribution is unlimited.		
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE				
4. PERFORMING ORGANIZATION REPORT NUMBER(S) SLCET-TR-89-5		5. MONITORING ORGANIZATION REPORT NUMBER(S)		
6a. NAME OF PERFORMING ORGANIZATION US Army Laboratory Command Electronics Tech & Devices Lab		6b. OFFICE SYMBOL (if applicable) SLCET-MA-A	7a. NAME OF MONITORING ORGANIZATION	
6c. ADDRESS (City, State, and ZIP Code) Electronics Technology and Devices Laboratory ATTN: SLCET-MA-A Fort Monmouth, NJ 07703-5000		7b. ADDRESS (City, State, and ZIP Code)		
8a. NAME OF FUNDING / SPONSORING ORGANIZATION	8b. OFFICE SYMBOL (if applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER		
8c. ADDRESS (City, State, and ZIP Code)		10. SOURCE OF FUNDING NUMBERS		
		PROGRAM ELEMENT NO. 1L162705	PROJECT NO. H94	TASK NO. K9
11. TITLE (Include Security Classification) POLARIZATION MATRICES OF QUARTZ (U)				
12. PERSONAL AUTHOR(S) Arthur Ballato and Theodore Lukaszek				
13a. TYPE OF REPORT Technical Report	13b. TIME COVERED FROM Jan 88 to Jan 89	14. DATE OF REPORT (Year, Month, Day) 1989 July	15. PAGE COUNT 26	
16. SUPPLEMENTARY NOTATION				
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number) Piezoelectric resonators; piezoelectric transducers; quartz crystals; acousto-optics		
FIELD	GROUP			SUB-GROUP
09	01			
17	02			
19. ABSTRACT (Continue on reverse if necessary and identify by block number) In analytical treatments of piezoelectric-acoustic transducers, signal processors, and resonators, the electromechanical transduction mechanism is most often expressed in terms of the elements of the piezoelectric [e] or [d] matrices. Molecular interpretations of piezoelectricity, and especially electrooptical applications, usually involve polarization as the preferred variable, and consequently the alternative [a] and [b] matrices are of interest. The elements of these latter sets are calculated for quartz from measured elastopiezodielectric constants taken from the literature.				
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified		
22a. NAME OF RESPONSIBLE INDIVIDUAL Dr. Arthur Ballato		22b. TELEPHONE (Include Area Code) (201) 544-2773	22c. OFFICE SYMBOL SLCET-MA-A	

DD Form 1473, JUN 86

Previous editions are obsolete.

SECURITY CLASSIFICATION OF THIS PAGE

UNCLASSIFIED

## CONTENTS

	Page
INTRODUCTION . . . . .	1
CONSTITUTIVE EQUATION SETS . . . . .	1
RELATIONS AMONG MATERIAL CONSTANTS . . . . .	5
CALCULATION SEQUENCE . . . . .	7
EXPLICIT FORMULAS FOR POINT GROUP 32 . . . . .	10
INPUT VALUES FOR QUARTZ . . . . .	16
OUTPUT VALUES FOR QUARTZ . . . . .	16
CONCLUSIONS. . . . .	19
REFERENCES . . . . .	19

## TABLES

Table	Page
1. Symbols, Units, and Definitions . . . . .	2
2. Relations among Material Constants . . . . .	8
3. Further Relations among Material Constants . . . . .	9
4. Elastopiezodielectric Matrices for Point Group 32: The [e], [h], and [a] Sets . . . . .	11
5. Elastopiezodielectric Matrices for Point Group 32: The [d], [g], and [b] Sets . . . . .	11
6. Isagric Elastic Stiffnesses . . . . .	16
7. Piezoelectric Stress Constants . . . . .	16
8. Dielectric Permittivities at Constant Strain . . . . .	16
9. Elastic Stiffnesses . . . . .	17
10. Elastic Compliances . . . . .	17

Table	Page
11. Piezoelectric [e], [h], and [a] Values . . . . .	17
12. Piezoelectric [d], [g], and [b] Values . . . . .	18
13. Dielectric (eps) Values . . . . .	18
14. Dielectric (chi) Values . . . . .	18
15. Dielectric (bet) Values . . . . .	18
16. Dielectric (zet) Values . . . . .	19

Address	
NTIS Grant	<input checked="" type="checkbox"/>
ERIC Fee	<input type="checkbox"/>
Charge Card	<input type="checkbox"/>
Justification	
By _____	
District _____	
Additional Copies	
_____	
_____	
_____	
Dist _____	
_____	
A-1	



## INTRODUCTION

Electromechanical transduction taking place via the piezoelectric effect is characterized phenomenologically by constitutive equations that relate the elastic and electric variables. These equations take a variety of forms, depending upon the choice of independent and dependent variables; the choice is normally dictated by the application. For example, piezoelectric resonators in the form of thickness mode plates are most easily treated using the isagric elastic stiffnesses  $[cE]$ , the piezoelectric stress constants  $[e]$ , and the dielectric permittivities at constant strain  $[(\epsilon)S]$ .

Various measurement techniques yield values for the elements of a particular coefficient set more directly than those of another. The coefficients appearing in the different equation sets are, however, interrelated, so that once any one complete set is available, all the other sets of elements may be found. The most accurate and precise experimental results to date have been from plate resonator (resonance) and pulse-echo (transit-time) measurements. From the  $[cE]$ ,  $[e]$ , and  $[(\epsilon)S]$  matrices determined therefrom, those matrices representing material properties expressed in the other alternative forms may be calculated.

Electrooptical applications are becoming increasingly important. So also are treatments of piezoelectric and ferroelectric phenomena from the standpoint of molecular interactions. In both of these cases the constitutive equations using polarization as the independent electrical variable, rather than either electric intensity or displacement, assume greater importance than the sets traditionally used for transducer, signal processing, and resonator applications.

In this report we give the complete sets of linear constitutive equations relating elastic and electric fields. For each equation set the numerical values are computed for quartz, from the measured  $[cE]$ ,  $[e]$ , and  $[(\epsilon)S]$  values of Bechmann (Ref. 1). Coupling to the thermal field is neglected. Rationalized mks units are used throughout.

## CONSTITUTIVE EQUATION SETS

Symbols and units for the quantities employed are given in Table 1. In terms of these, six constitutive equation sets are used. Of these, electric intensity, dielectric displacement, and polarization each appear in two sets as an independent variable. The sets are, in compressed matrix notation, as follows. A prime denotes transpose;  $[I]$  is the unit matrix.

### I. The Piezoelectric Stress Constant Set

$$\begin{aligned} [T] &= [cE] [S] - [e]' [E] & (1) \\ [D] &= [e] [S] + [(\epsilon)S] [E] & (2) \end{aligned}$$

TABLE 1. SYMBOLS, UNITS, AND DEFINITIONS.

QUANTITY	UNIT	SYMBOL/DEFINITION
Elastic stress	N/m <sup>2</sup>	[T]
Elastic strain	-----	[S]
Electric intensity	V/m	[E]
Dielectric displacement	C/m <sup>2</sup>	[D]
Dielectric polarization	C/m <sup>2</sup>	[P]
Elastic compliance at constant [E], [D], [P]	m <sup>2</sup> /N	[sE], [sD], [sP]
Elastic stiffness at constant [E], [D], [P]	N/m <sup>2</sup>	[cE], [cD], [cP]
Dielectric permittivity at constant [T], [S]	F/m	[( $\epsilon$ s)T], [( $\epsilon$ s)S]
Dielectric constant, relative, at constant [T], [S]	-----	[( $\epsilon$ r)T], [( $\epsilon$ r)S] =[( $\epsilon$ s)T]/( $\epsilon$ s) <sub>o</sub> , [( $\epsilon$ s)S]/( $\epsilon$ s) <sub>o</sub>
Dielectric impermeability at constant [T], [S]	m/F	[( $\beta$ t)T], [( $\beta$ t)S] =[( $\epsilon$ s)T] <sup>(-1)</sup> , [( $\epsilon$ s)S] <sup>(-1)</sup>
Dielectric impermeability, relative, at constant [T], [S]	-----	[( $\beta$ tr)T], [( $\beta$ tr)S] =[( $\beta$ t)T]*( $\epsilon$ s) <sub>o</sub> , [( $\beta$ t)S]*( $\epsilon$ s) <sub>o</sub> =[( $\epsilon$ r)T] <sup>(-1)</sup> , [( $\epsilon$ r)S] <sup>(-1)</sup>
Dielectric susceptibility at constant [T], [S]	F/m	[( $\chi$ i)T], [( $\chi$ i)S] =[( $\epsilon$ r)T-I]*( $\epsilon$ s) <sub>o</sub> , [( $\epsilon$ r)S-I]*( $\epsilon$ s) <sub>o</sub>
Dielectric susceptibility, relative, at constant [T], [S]	-----	[( $\chi$ ir)T], [( $\chi$ ir)S] =[( $\chi$ i)T]/( $\epsilon$ s) <sub>o</sub> , [( $\chi$ i)S]/( $\epsilon$ s) <sub>o</sub>
Reciprocal dielectric susceptibility at constant [T], [S]	m/F	[( $\zeta$ t)T], [( $\zeta$ t)S] =[( $\chi$ i)T] <sup>(-1)</sup> , [( $\chi$ i)S] <sup>(-1)</sup>
Reciprocal dielectric susceptibility, relative, at constant [T], [S]	-----	[( $\zeta$ tr)T], [( $\zeta$ tr)S] =[( $\zeta$ t)T]*( $\epsilon$ s) <sub>o</sub> , [( $\zeta$ t)S]*( $\epsilon$ s) <sub>o</sub>
Piezoelectric stress constant	C/m <sup>2</sup>	[e]

TABLE 1. SYMBOLS, UNITS, AND DEFINITIONS. (continued)

QUANTITY	UNIT	SYMBOL/DEFINITION
Piezoelectric strain coefficient	$m/V = C/N$	[d]
Piezoelectric stress modulus	$N/C = V/m$	[h]
Piezoelectric strain constant	$m^2/C$	[g]
Piezoelectric polarization modulus	$V/m = N/C$	[a]
Piezoelectric polarization constant	$m^2/C$	[b]

Note: Square brackets, sic: [ ], denote matrices.

II. The Piezoelectric Strain Coefficient Set

$$\begin{aligned} [S] &= [sE] [T] + [d]' [E] & (3) \\ [D] &= [d] [T] + [(\epsilon)sT] [E] & (4) \end{aligned}$$

III. The Piezoelectric Stress Modulus Set

$$\begin{aligned} [T] &= [cD] [S] - [h]' [D] & (5) \\ [E] &= -[h] [S] + [(\beta)s] [D] & (6) \end{aligned}$$

IV. The Piezoelectric Strain Constant Set

$$\begin{aligned} [S] &= [sD] [T] + [g]' [D] & (7) \\ [E] &= -[g] [T] + [(\beta)sT] [D] & (8) \end{aligned}$$

V. The Piezoelectric Polarization Modulus Set

$$\begin{aligned} [T] &= [cP] [S] - [a]' [P] & (9) \\ [E] &= -[a] [S] + [(\zeta)s] [P] & (10) \end{aligned}$$

VI. The Piezoelectric Polarization Constant Set

$$\begin{aligned} [S] &= [sP] [T] + [b]' [P] & (11) \\ [E] &= -[b] [T] + [(\zeta)sT] [P] & (12) \end{aligned}$$

The electric variables are connected by the relation

$$[D] = (\epsilon)s_0 * [E] + [P] \quad (13)$$

where  $(\epsilon)s_0$  is the permittivity of free space, defined by

$$(\epsilon)s_0 * (\mu)s_0 * (c) * (c) = 1 ; \quad (14)$$

$(\mu)s_0$  is the permeability of free space, equal, by definition, to  $4 \pi * 10^{(-7)}$ , and  $(c)$  is the velocity of light in vacuo and, also by definition, is equal exactly to  $2.99792458 * 10^8$  m/s.

From (13) the expressions for the remaining electric variables associated, respectively, with the six equation sets ( 1) to (12) may be found:

$$[P] = [e] [S] + [(\chi)s] [E] \quad (15)$$

$$[P] = [d] [T] + [(\chi)sT] [E] \quad (16)$$

$$[P] = (\epsilon)s_0 * [h] [S] + [I - (\epsilon)s_0 * (\beta)s] [D] \quad (17)$$

$$[P] = (\epsilon)s_0 * [g] [T] + [I - (\epsilon)s_0 * (\beta)sT] [D] \quad (18)$$

$$[D] = -(\epsilon)_o * [a] [S] + [I + (\epsilon)_o * (\zeta)S] [P] \quad (19)$$

$$[D] = -(\epsilon)_o * [b] [T] + [I + (\epsilon)_o * (\zeta)T] [P] \quad (20)$$

#### RELATIONS AMONG MATERIAL CONSTANTS

The material constants are interrelated by the following formulas:

$$[cX] [sX] = [(\epsilon)_Y] [(\beta)_Y] = [I] \quad (21)$$

$$[(\chi)_Y] [(\zeta)_Y] = [(K_r)_Y - (\chi)_Y] = [I] \quad (22)$$

In (21) and (22), X = E, D, or P and Y = T or S.

$$\begin{aligned} [cD] - [cE] &= [h]' [e] = [e]' [h] \\ &= [h]' [(\epsilon)_S] [h] = [e]' [(\beta)_S] [e] \\ &= [a]' [e - h * (\epsilon)_o] = [e - h * (\epsilon)_o]' [a] \end{aligned} \quad (23)$$

$$\begin{aligned} [cP] - [cD] &= [h]' [a] * (\epsilon)_o = [a]' [h] * (\epsilon)_o \\ &= [h]' [(\epsilon)_S] [(\zeta)_S] [h] * (\epsilon)_o \\ &= [a]' [(\beta)_S] [(\chi)_S] [a] * (\epsilon)_o \\ &= [a - h]' [e] = [e]' [a - h] \end{aligned} \quad (24)$$

$$\begin{aligned} [cP] - [cE] &= [a]' [e] = [e]' [a] \\ &= [a]' [(\chi)_S] [a] = [e]' [(\zeta)_S] [e] \\ &= [h]' [e + a * (\epsilon)_o] = [e + a * (\epsilon)_o]' [h] \end{aligned} \quad (25)$$

$$\begin{aligned} [sE] - [sD] &= [d]' [g] = [g]' [d] \\ &= [d]' [(\beta)_T] [d] = [g]' [(\epsilon)_T] [g] \\ &= [h]' [d - g * (\epsilon)_o] = [d - g * (\epsilon)_o]' [b] \end{aligned} \quad (26)$$

$$\begin{aligned} [sD] - [sP] &= [b]' [g] * (\epsilon)_o = [g]' [b] * (\epsilon)_o \\ &= [g]' [(\epsilon)_T] [(\zeta)_T] [g] * (\epsilon)_o \\ &= [b]' [(\beta)_T] [(\chi)_T] [b] * (\epsilon)_o \\ &= [b - g]' [d] = [d]' [b - g] \end{aligned} \quad (27)$$

$$\begin{aligned} [sE] - [sP] &= [b]' [d] = [d]' [b] \\ &= [b]' [(\chi)_T] [b] = [d]' [(\zeta)_T] [d] \\ &= [g]' [d + b * (\epsilon)_o] = [d + b * (\epsilon)_o]' [g] \end{aligned} \quad (28)$$

$$\begin{aligned}
[(\text{zet})S] - [(\text{zet})T] &= [b] [a]' = [a] [b]' \\
&= [b] [cP] [b]' = [a] [sP] [a]' \tag{29}
\end{aligned}$$

$$\begin{aligned}
[(\text{chi})T] - [(\text{chi})S] &= [(\text{eps})T] - [(\text{eps})S] \\
&= [e] [d]' = [d] [e]' \\
&= [d] [cE] [d]' = [e] [sE] [e]' \tag{30}
\end{aligned}$$

$$\begin{aligned}
[(\text{bet})S] - [(\text{bet})T] &= [h] [g]' = [g] [h]' \\
&= [g] [cD] [g]' = [h] [sD] [h]' \tag{31}
\end{aligned}$$

$$[e] = [d] [cE] = [(\text{eps})S] [h] = [(\text{chi})S] [a] \tag{32}$$

$$[d] = [e] [sE] = [(\text{eps})T] [g] = [(\text{chi})T] [b] \tag{33}$$

$$\begin{aligned}
[h] = [g] [cD] &= [(\text{bet})S] [e] = [(\text{chi})S] [(\text{bet})S] [a] \\
&= [I - (\text{bet})S * (\text{eps})o] [a] \tag{34}
\end{aligned}$$

$$\begin{aligned}
[g] = [h] [sD] &= [(\text{bet})T] [d] = [(\text{chi})T] [(\text{bet})T] [b] \\
&= [I - (\text{bet})T * (\text{eps})o] [b] \tag{35}
\end{aligned}$$

$$\begin{aligned}
[a] = [b] [cP] &= [(\text{zet})S] [e] = [(\text{eps})S] [(\text{zet})S] [h] \\
&= [I + (\text{zet})S * (\text{eps})o] [h] \tag{36}
\end{aligned}$$

$$\begin{aligned}
[b] = [a] [sP] &= [(\text{zet})T] [d] = [(\text{eps}' T] [(\text{zet})T] [g] \\
&= [I + (\text{zet})T * (\text{eps})o] [g] \tag{37}
\end{aligned}$$

Some alternative relations are the following:

$$\begin{aligned}
[a - h] &= [(\text{zet})S] [h] * (\text{eps})o \\
&= [(\text{bet})S] [a] * (\text{eps})o \tag{38}
\end{aligned}$$

$$\begin{aligned}
[b - g] &= [(\text{zet})T] [g] * (\text{eps})o \\
&= [(\text{bet})T] [b] * (\text{eps})o \tag{39}
\end{aligned}$$

$$[e + a * (\text{eps})o] = [(\text{eps})S] [a] \tag{40}$$

$$[d + b * (\text{eps})o] = [(\text{eps})T] [b] \tag{41}$$

$$[e - h * (\text{eps})o] = [(\text{chi})S] [h] \tag{42}$$

$$[d - g * (\text{eps})o] = [(\text{chi})T] [g] \tag{43}$$

Equations (21) to (43) result from equating like dependent variables in pairs selected from equations ( 1) to (12) and (15) to (20). Each

pair yields one equation in three variables, one mechanical and two electrical, or vice versa. Two other equations exist, again from (1) to (12) and (15) to (20), that contain the same three variables found in each paired equation. One of these auxiliary equations is used to eliminate one of the two variables of the same kind; the result is one equation in two variables, one electrical and one mechanical. These are now independent variables, so the coefficients must vanish; two relations between the material coefficients result. As an example, (3) and (7) both have [S] as dependent variable. Equating them produces one relation in [T], [E], and [D]; one of the electrical variables must be eliminated. This is done by using either (4) or (8); each contains the same three variables. If (8) is used to eliminate [E], one obtains  $[sE - d'g - sD] [T] = [d'(\text{bet})T - g'] [D]$ . Therefore,  $[sE] - [sD] = [d]'$  [g] and  $[g] = [(\text{bet})T] [d]$ . Use of (4) instead of (8) leads to the equations  $[sE] - [sD] = [g]'$  [d] and  $[d] = [(\text{eps})T] [g]$ . There are 36 pairs, six each equating [S] and [T], and eight each equating [E], [D], and [P]. The 72 relations contain many redundancies. Relations between the elastic, piezoelectric, and dielectric constants are shown schematically in Tables 2 and 3.

#### CALCULATION SEQUENCE

Using as input  $[cE]$ ,  $[e]$ , and  $[(\text{eps})S]$ , one may compute the remaining quantities in a variety of ways. The following sequence is typical:

$$[sE] = [cE] \quad (-1) \quad (44)$$

$$[(\text{bet})S] = [(\text{eps})S] \quad (-1) \quad (45)$$

$$[d] = [e] [sE] \quad (46)$$

$$[h] = [(\text{bet})S] [e] \quad (47)$$

$$[(\text{eps})T] - [(\text{eps})S] = [e] [d]' \quad (48)$$

$$[(\text{eps})T] = [(\text{eps})S] + [e] [d]' \quad (49)$$

$$[(\text{bet})T] = [(\text{eps})T] \quad (-1) \quad (50)$$

$$[cD] - [cE] = [e]' [h] \quad (51)$$

$$[cD] = [cE] + [e]' [h] \quad (52)$$

$$[g] = [(\text{bet})T] [d] \quad (53)$$

$$[sE] - [sD] = [d]' [g] \quad (54)$$

$$[sD] = [sE] - [d]' [g] \quad (55)$$

$$[(\text{betr})S] = [(\text{bet})S] * (\text{eps})_0 \quad (56)$$

$$[(\text{zetr})S] = [(\text{betr})S] [I - (\text{betr})S] \quad (-1) \quad (57)$$

TABLE 2. RELATIONS AMONG MATERIAL CONSTANTS.


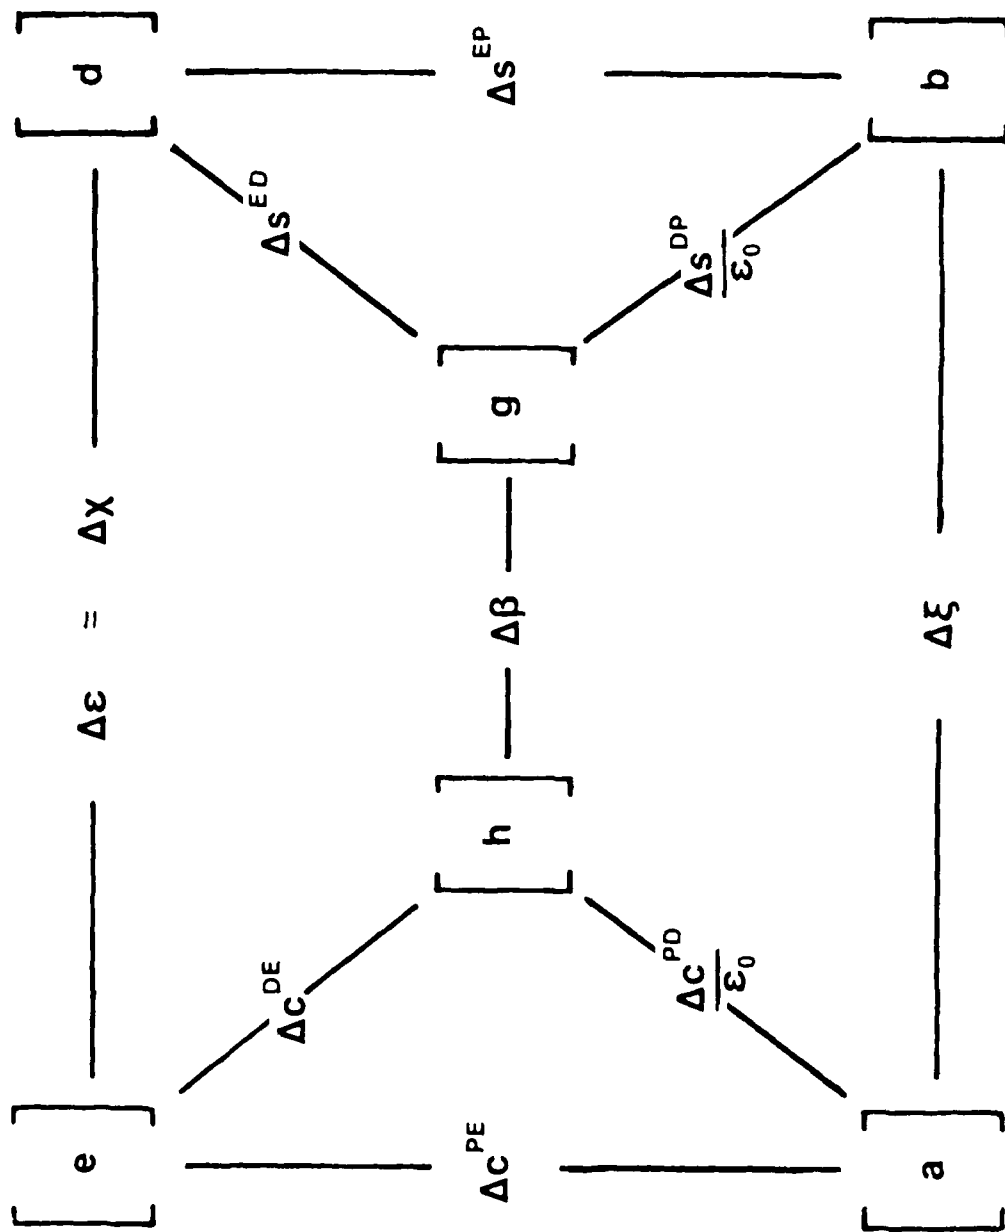


TABLE 3. FURTHER RELATIONS AMONG MATERIAL CONSTANTS.

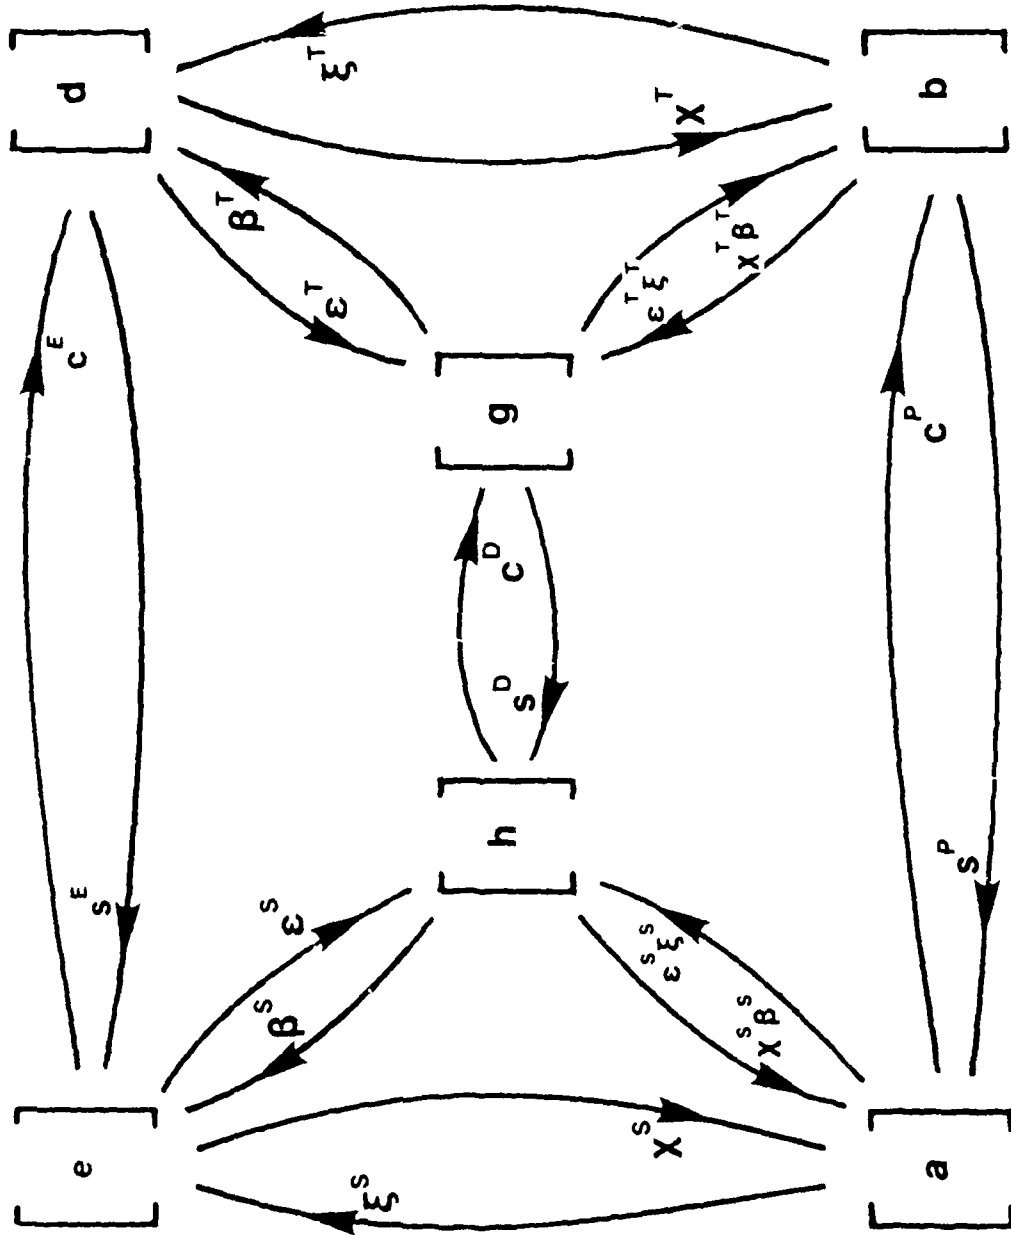

$$[(\text{zet})S] = [(\text{zetr})] / (\text{eps})_0 \quad (58)$$

$$[(\text{betr})T] = [(\text{bet})T] * (\text{eps})_0 \quad (59)$$

$$[(\text{zetr})T] = [(\text{betr})T] [I - (\text{betr})T]^{-1} \quad (60)$$

$$[(\text{zet})T] = [(\text{zetr})T] / (\text{eps})_0 \quad (61)$$

$$[(\text{chi})S] = [(\text{zet})S]^{-1} \quad (62)$$

$$[(\text{chi})T] = [(\text{zet})T]^{-1} \quad (63)$$

$$[a] = [(\text{zet})S] [e] \quad (64)$$

$$[b] = [(\text{zet})T] [d] \quad (65)$$

$$[cP] - [cE] = [e]' [a] \quad (66)$$

$$[cP] = [cE] + [e]' [a] \quad (67)$$

$$[cP] - [cD] = [a]' [h] * (\text{eps})_0 \quad (68)$$

$$[sE] - [sP] = [d]' [b] \quad (69)$$

$$[sP] = [sE] - [d]' [b] \quad (70)$$

$$[sD] - [sP] = [g]' [b] * (\text{eps})_0 \quad (71)$$

$$[(\text{bet})S] - [(\text{bet})T] = [h] [g]' \quad (72)$$

$$[(\text{chi})T] - [(\text{chi})S] = [(\text{eps})T] - [(\text{eps})S] \quad (73)$$

$$[(\text{zet})S] - [(\text{zet})T] = [a] [b]' \quad (74)$$

A number of these relations are used as checks. For example,  $[(\text{bet})S]$  and  $[(\text{bet})T]$  are known from (45) and (50), but the difference is recomputed in (72).

#### EXPLICIT FORMULAS FOR POINT GROUP 32

Elastic:

The 6x6 elastic constant portions of Tables 4 and 5 partition into 4x4 and 2x2 submatrices. The 4x4 elastic stiffness and compliance submatrices are interrelated by formulas (75) to (93), taken from Cady (Ref. 2):

$$A = s_{33} * (s_{11} + s_{12}) - 2 * s_{13} * s_{13} \quad (75)$$

$$B = s_{44} * (s_{11} - s_{12}) - 2 * s_{14} * s_{14} \quad (76)$$

$$2 * c_{11} = s_{33} / A + s_{44} / B \quad (77)$$

$$2 * c_{12} = s_{33} / A - s_{44} / B \quad (78)$$

TABLE 4. ELASTOPIEZODIELECTRIC MATRICES FOR POINT GROUP 32:  
THE [e], [h], AND [a] SETS.

11	12	13	14	00	00	]	11	00	00		
						]				cE ]	e'
12	11	13	-14	00	00	]	-11	00	00	----	-----
						]				e ]	(eps)S
13	13	33	00	00	00	]	00	00	00		
						]					
14	-14	00	44	00	00	]	14	00	00		
						]				cD ]	h'
00	00	00	00	44	14	]	00	-14	00	----	-----
						]				h ]	(bet)S
00	00	00	00	14	66	]	00	-11	00		
-----											
11	-11	00	14	00	00	]	11	00	00		
						]				cP ]	a'
00	00	00	00	-14	-11	]	00	11	00	----	-----
						]				a ]	(zet)S
00	00	00	00	00	00	]	00	00	33		

$$66 = (11 - 12) / 2$$

Matrix entries show only subscripts.

TABLE 5. ELASTOPIEZODIELECTRIC MATRICES FOR POINT GROUP 32:  
THE [d], [g], AND [b] SETS.

11	12	13	14	00	00	]	11	00	00		
						]				sE ]	d'
12	11	13	-14	00	00	]	-11	00	00	----	-----
						]				d ]	(eps)T
13	13	33	00	00	00	]	00	00	00		
						]					
14	-14	00	44	00	00	]	14	00	00		
						]				sD ]	g'
00	00	00	00	44	14*2	]	00	-14	00	----	-----
						]				g ]	(bet)T
00	00	00	00	14*2	66	]	00	-11*2	00		
-----											
11	-11	00	14	00	00	]	11	00	00		
						]				sP ]	b'
00	00	00	00	-14	-11*2	]	00	11	00	----	-----
						]				b ]	(zet)T
00	00	00	00	00	00	]	00	00	33		

$$66 = (11 - 12) * 2$$

Matrix elements show only subscripts.

$$c_{13} = -s_{13} / A ; \quad c_{14} = -s_{14} / B \quad (79a), (79b) \quad (79)$$

$$c_{33} = (s_{11} + s_{12}) / A \quad (80)$$

$$c_{44} = (s_{11} - s_{12}) / B \quad (81)$$

$$c_{66} = (c_{11} - c_{12}) / 2 = s_{44} / (2 * E) \quad (82)$$

$$K = c_{33} * (c_{11} + c_{12}) - 2 * c_{13} * c_{13} \quad (83)$$

$$L = c_{44} * (c_{11} - c_{12}) - 2 * c_{14} * c_{14} \quad (84)$$

$$2 * s_{11} = c_{33} / K + c_{44} / L \quad (85)$$

$$2 * s_{12} = c_{33} / K - c_{44} / L \quad (86)$$

$$s_{13} = -c_{13} / K ; \quad s_{14} = -c_{14} / L \quad (87a), (87b) \quad (87)$$

$$s_{33} = (c_{11} + c_{12}) / K \quad (88)$$

$$s_{44} = (c_{11} - c_{12}) / L \quad (89)$$

$$s_{66} = (s_{11} - s_{12}) = 2 * c_{44} / L \quad (90)$$

$$\det (4 \times 4) [s] = A * B \quad (91)$$

$$\det (4 \times 4) [c] = K * L \quad (92)$$

$$A * K = B * L = A * B * K * L = 1 \quad (93)$$

Formulas (75) to (93) hold for each set of constant electrical conditions: either E, D, or P constant.

$$[cD] - [cE] = [\text{del } cDE] = [e]' [h] = [h]' [e] \quad (23)$$

$$\text{del } cDE_{11} = + e_{11} h_{11} \quad (94)$$

$$\text{del } cDE_{12} = - e_{11} h_{11} \quad (95)$$

$$\text{del } cDE_{13} = 0 \quad (96)$$

$$\text{del } cDE_{14} = + e_{11} h_{14} = + h_{11} e_{14} \quad (97)$$

$$\text{del } cDE_{33} = 0 \quad (98)$$

$$\text{del } cDE_{44} = + e_{14} h_{14} \quad (99)$$

$$\text{del } cDE_{66} = + e_{11} h_{11} \quad (100)$$

$$\begin{aligned} [cP] - [cD] &= [\text{del } cPD] = [a]' [h] * (\text{eps})_o \\ &= [h]' [a] * (\text{eps})_o \end{aligned} \quad (24)$$

$$\text{del } cPD_{11} = ( + a_{11} h_{11} ) * (\text{eps})_o \quad (101)$$

$$\text{del cPD12} = ( - a_{11} h_{11} ) * (\text{eps})_o \quad (102)$$

$$\text{del cPD13} = 0 \quad (103)$$

$$\begin{aligned} \text{del cPD14} &= ( + a_{11} h_{14} ) * (\text{eps})_o \\ &= ( + h_{11} a_{14} ) * (\text{eps})_o \end{aligned} \quad (104)$$

$$\text{del cPD33} = 0 \quad (105)$$

$$\text{del cPD44} = ( + a_{14} h_{14} ) * (\text{eps})_o \quad (106)$$

$$\text{del cPD66} = ( + a_{11} h_{11} ) * (\text{eps})_o \quad (107)$$

$$[cP] - [cE] = [\text{del cPE}] = [e]' [a] = [a]' [e] \quad (25)$$

$$\text{del cPE11} = + e_{11} a_{11} \quad (108)$$

$$\text{del cPE12} = - e_{11} a_{11} \quad (109)$$

$$\text{del cPE13} = 0 \quad (110)$$

$$\text{del cPE14} = + e_{11} a_{14} = + a_{11} e_{14} \quad (111)$$

$$\text{del cPE33} = 0 \quad (112)$$

$$\text{del cPE44} = + e_{14} a_{14} \quad (113)$$

$$\text{del cPE66} = + e_{11} a_{11} \quad (114)$$

From the del c14 entries we have the ratios

$$e_{11} / e_{14} = h_{11} / h_{14} = a_{11} / a_{14}. \quad (115), (116)$$

$$[sE] - [sD] = [\text{del sED}] = [d]' [g] = [g]' [d] \quad (26)$$

$$\text{del sED11} = + d_{11} g_{11} \quad (117)$$

$$\text{del sED12} = - d_{11} g_{11} \quad (118)$$

$$\text{del sED13} = 0 \quad (119)$$

$$\text{del sED14} = + d_{11} g_{14} = + g_{11} d_{14} \quad (120)$$

$$\text{del sED33} = 0 \quad (121)$$

$$\text{del sED44} = + d_{14} g_{14} \quad (122)$$

$$\text{del sED66} = + d_{11} g_{11} * 4 \quad (123)$$

$$[sD] - [sP] = [g]' [b] * (\text{eps})_o$$

$$= [b]' [g] * (\text{eps})_o \quad (27)$$

$$\text{del sDP11} = ( + g_{11} b_{11} ) * (\text{eps})_o \quad (124)$$

$$\text{del sDP12} = ( - g_{11} b_{11} ) * (\text{eps})_o \quad (125)$$

$$\text{del sDP13} = 0 \quad (126)$$

$$\begin{aligned} \text{del sDP14} &= ( + g_{11} b_{14} ) * (\text{eps})_o \\ &= ( + b_{11} g_{14} ) * (\text{eps})_o \end{aligned} \quad (127)$$

$$\text{del sDP33} = 0 \quad (128)$$

$$\text{del sDP44} = ( - g_{14} b_{14} ) * (\text{eps})_o \quad (129)$$

$$\text{del sDP66} = ( + g_{11} b_{11} ) * 4 * (\text{eps})_o \quad (130)$$

$$[sE] - [sP] = [\text{del sEP}] = [b]' [d] = [d]' [b] \quad (28)$$

$$\text{del sEP11} = + d_{11} b_{11} \quad (131)$$

$$\text{del sEP12} = - d_{11} b_{11} \quad (132)$$

$$\text{del sEP13} = 0 \quad (133)$$

$$\text{del sEP14} = + d_{11} b_{14} = + b_{11} d_{14} \quad (134)$$

$$\text{del sEP33} = 0 \quad (135)$$

$$\text{del sEP44} = + d_{14} b_{14} \quad (136)$$

$$\text{del sEP66} = + d_{11} b_{11} * 4 \quad (137)$$

From the del s14 entries we have the ratios

$$d_{11} / d_{14} = g_{11} / g_{14} = b_{11} / b_{14}. \quad (138), (139)$$

Piezoelectric:

$$[d] = [e] [sE] \quad (33)$$

$$d_{14} = + e_{14} sE_{44} + e_{11} sE_{14} * 2 \quad (140)$$

$$d_{11} = + e_{11} (sE_{11} - sE_{12}) + e_{14} sE_{14} \quad (141)$$

$$[h] = [(bet)S] [e] \quad (34)$$

$$h_{14} = (bet)S_{11} e_{14} \quad (142)$$

$$h_{11} = (bet)S_{11} e_{11} \quad (143)$$

$$[g] = [(\text{bet})T] [d] \quad (35)$$

$$g_{14} = (\text{bet})T_{11} d_{14} \quad (144)$$

$$g_{11} = (\text{bet})T_{11} d_{11} \quad (145)$$

$$[a] = [(\text{zet})S] [e] \quad (36)$$

$$a_{14} = (\text{zet})S_{11} e_{14} \quad (146)$$

$$a_{11} = (\text{zet})S_{11} e_{11} \quad (147)$$

$$[b] = [(\text{zet})T] [d] \quad (37)$$

$$b_{14} = (\text{zet})T_{11} d_{14} \quad (148)$$

$$b_{11} = (\text{zet})T_{11} d_{11} \quad (149)$$

Dielectric:

$$[(\text{bet})Y] = [(\text{eps})Y]^{-1} \quad (21)$$

$$(\text{bet})Y_{11} = 1 / (\text{eps})Y_{11} \quad (150)$$

$$(\text{bet})Y_{33} = 1 / (\text{eps})Y_{33} \quad (151)$$

$$[(\text{zetr})Y] = [(\text{betr})Y] [I - (\text{betr})Y]^{-1} \quad (152)$$

$$(\text{zet})Y_{11} = 1 / ((\text{eps})Y_{11} - (\text{eps})_0) \quad (153)$$

$$(\text{zet})Y_{33} = 1 / ((\text{eps})Y_{33} - (\text{eps})_0) \quad (154)$$

$$[(\text{eps})T - (\text{eps})S] = [\text{del} (\text{eps})] = [e] [d]' =$$

$$[(\text{chi})T - (\text{chi})S] = [\text{del} (\text{chi})] = [d] [e]' \quad (30)$$

$$\text{del} (\text{eps})_{11} = \text{del} (\text{chi})_{11} = + e_{14} d_{14} + e_{11} d_{11} * 2 \quad (155)$$

$$\text{del} (\text{eps})_{33} = \text{del} (\text{chi})_{33} = 0 \quad (156)$$

$$[(\text{bet})S - (\text{bet})T] = [h] [g]' = [g] [h]' \quad (31)$$

$$\text{del} (\text{bet})_{11} = + h_{14} g_{14} + h_{11} g_{11} * 2 \quad (157)$$

$$\text{del} (\text{bet})_{33} = 0 \quad (158)$$

$$[(\text{zet})S - (\text{zet})T] = [\text{del} (\text{zet})] = [a] [b]' = [b] [a]' \quad (159)$$

$$\text{del} (\text{zet})_{11} = + a_{14} b_{14} + a_{11} b_{11} * 2 \quad (160)$$

$$\text{del} (\text{zet})_{33} = 0 \quad (161)$$

INPUT VALUES FOR QUARTZ

The values measured by Bechmann (Ref. 1) are as follows:

TABLE 6. ISAGRIC ELASTIC STIFFNESSES.

cE11	cE12	cE13	cE14	cE33	cE44	cE66
86.74	6.98*	11.91	-17.91	107.2	57.94	39.88

Units:  $10^{(9)}$  N/m<sup>2</sup>

\* The value of 6.99 appearing in Ref. 1 has been changed so that the relation  $c66 = (c11 - c12)/2$  holds; c11 and c66 are directly measured and hence are more accurately known than c12.

TABLE 7. PIEZOELECTRIC STRESS CONSTANTS.

e11	e14
0.171	-0.0406

Units: C/m<sup>2</sup>

TABLE 8. DIELECTRIC PERMITTIVITIES AT CONSTANT STRAIN.

(eps)S11	(eps)S33
39.21	41.03

Units:  $10^{(-12)}$  F/m

OUTPUT VALUES FOR QUARTZ

The input values from Tables 6, 7, and 8 were used to compute the remaining elastic, piezoelectric, and dielectric quantities for quartz in the manner discussed in prior sections of this report. The results are given in Tables 9 to 16.

TABLE 9. ELASTIC STIFFNESSES.

	cE	cD	cP	del cDE	del cPE	del cPD
11	86.74	87.49	87.70	0.746	0.963	0.218
12	6.98*	6.23	6.02	-0.746	-0.963	-0.218
13	11.91	11.91	11.91	0	0	0
14	-17.91	-18.09	-18.14	-0.177	-0.229	-0.0516
33	107.2	107.2	107.2	0	0	0
44	57.94	57.98	57.99	0.0420	0.0543	0.0123
66	39.88	40.63	40.84	0.746	0.963	0.218

Units:  $10^{(9)}$  N/m<sup>2</sup>

\* The value of 6.99 appearing in Ref. 1 has been changed so that the relation  $c_{66} = (c_{11} - c_{12})/2$  holds;  $c_{11}$  and  $c_{66}$  are directly measured and hence are more accurately known than  $c_{12}$ .

TABLE 10. ELASTIC COMPLIANCES.

	sE	sD	sP	del sED	del sEP	del sDP
11	12.77	12.64	12.60	0.133	0.171	0.0379
12	-1.79	-1.66	-1.62	-0.133	-0.171	-0.0379
13	-1.22	-1.22	-1.22	0	0	0
14	4.50	4.46	4.45	0.0419	0.0538	0.0119
33	9.60	9.60	9.60	0	0	0
44	20.04	20.03	20.02	0.0132	0.0169	0.00375
66	29.12	28.58	28.43	0.533	0.684	0.152

Units:  $10^{(-12)}$  m<sup>2</sup>/N

TABLE 11. PIEZOELECTRIC [e], [h], AND [a] VALUES.

	e	h	a
11	0.171	4.36	5.63
14	-0.0406	-1.04	-1.34

Units: e: C/m<sup>2</sup>; h and a:  $10^{(9)}$  V/m

TABLE 12. PIEZOELECTRIC [d], [g], AND [b] VALUES.

	d	g	b
11	2.31	57.7	74.1
14	+0.725	18.1	23.3

Units: d:  $10^{-12}$  m/V; g and b:  $10^{-3}$  m<sup>2</sup>/C

TABLE 13. DIELECTRIC (eps) VALUES.

	(eps)S	(eps)T	del (eps)TS
11	39.21	39.97	0.759
33	41.03	41.03	0

Units:  $10^{-12}$  F/m.

del (eps)TS = del (chi)TS

TABLE 14. DIELECTRIC (chi) VALUES.

	(chi)S	(chi)T	del (chi)TS
11	30.36	31.12	0.759
33	32.18	32.18	0

Units:  $10^{-12}$  F/m.

del (chi)TS = del (eps)TS

TABLE 15. DIELECTRIC (bet) VALUES.

	(bet)S	(bet)T	del (bet)TS
11	25.50	25.02	-0.485
33	24.37	24.37	0

Units:  $10^{(9)}$  m/F.

TABLE 16. DIELECTRIC (zet) VALUES.

	(zet)S	(zet)T	del (zet)TS
11	32.94	32.14	-0.804
33	31.08	31.08	0

Units:  $10^{(9)}$  m/F.

#### CONCLUSIONS

This report provides formulas interrelating the coefficients that appear in the several alternative sets of constitutive equations involving the elastic, piezoelectric, and dielectric properties of crystals. These are then specialized for crystals of class 32; using measured values reported for quartz, numerical values of the elements of the polarization matrices are calculated.

#### REFERENCES

1. R. Bechmann, "Elastic and Piezoelectric Constants of Alpha-Quartz," Phys. Rev., Vol. 110, No. 5, June 1, 1958, pp. 1060-1061.
2. W. G. Cady, Piezoelectricity, McGraw-Hill, New York, 1946; Dover, New York, 1964.

ELECTRONICS TECHNOLOGY AND DEVICES LABORATORY  
MANDATORY DISTRIBUTION LIST  
CONTRACT OR IN-HOUSE TECHNICAL REPORTS

15 Nov 88  
Page 1 of 2

101 Defense Technical Information Center\*  
ATTN: DTIC-FDAC  
Cameron Station (Bldg 5) (\*Note: Two copies for DTIC will  
Alexandria, VA 22304-6145 be sent from STINFO Office.)

483 Director  
US Army Material Systems Analysis Actv  
ATTN: DRXSY-MP  
001 Aberdeen Proving Ground, MD 21005

563 Commander, AMC  
ATTN: AMCDE-SC  
5001 Eisenhower Ave.  
001 Alexandria, VA 22333-0001

609 Commander, LABCOM  
ATTN: AMSLC-CG, CO, CS (In turn)  
2800 Powder Mill Road  
001 Adelphi, Md 20783-1145

612 Commander, LABCOM  
ATTN: AMSLC-CT  
2800 Powder Mill Road  
001 Adelphi, MD 20783-1145

680 Commander,  
US Army Laboratory Command  
Fort Monmouth, NJ 07703-5000  
1 - SLCET-DD  
2 - SLCET-DT (M. Howard)  
1 - SLCET-DB  
35 - Originating Office

681 Commander, CECOM  
R&D Technical Library  
Fort Monmouth, NJ 07703-5000  
1 - ASQNC-ELC-I-T (Tech Library)  
3 - ASQNC-ELC-I-T (STINFO)

705 Advisory Group on Electron Devices  
201 Varick Street, 9th Floor  
002 New York, NY 10014-4877

ELECTRONICS TECHNOLOGY AND DEVICES LABORATORY  
SUPPLEMENTAL CONTRACT DISTRIBUTION LIST  
(ELECTIVE)

15 Nov 88  
Page 2 of 2

205	Director Naval Research Laboratory ATTN: CODE 2627	603	Cdr, Atmospheric Sciences Lab LABCOM ATTN: SLCAS-SY-S
001	Washington, DC 20375-5000	001	White Sands Missile Range, NM 88002
221	Cdr, PM JTFUSION ATTN: JTF 1500 Planning Research Drive	607	Cdr, Harry Diamond Laboratories ATTN: SLCHD-CO, TD (In turn) 2800 Powder Mill Road
001	McLean, VA 22102	001	Adelphi, MD 20783-1145
301	Rome Air Development Center ATTN: Documents Library (TILD)		
001	Griffiss AFB, NY 13441		
437	Deputy for Science & Technology Office, Asst Sec Army (R&D)		
001	Washington, DC 20310		
438	HQDA (DAMA-ARZ-D/Dr. F.D. Verderame)		
001	Washington, DC 20310		
520	Dir, Electronic Warfare/Reconnaissance Surveillance and Target Acquisition Ctr ATTN: AMSEL-EW-D		
001	Fort Monmouth, NJ 07703-5000		
523	Dir, Reconnaissance Surveillance and Target Acquisition Systems Directorate ATTN: AMSEL-EW-DR		
001	Fort Monmouth, NJ 07703-5000		
524	Cdr, Marine Corps Liaison Office ATTN: AMSEL-LN-MC		
001	Fort Monmouth, NJ 07703-5000		
564	Dir, US Army Signals Warfare Ctr ATTN: AMSEL-SW-OS Vint Hill Farms Station		
001	Warrenton, VA 22186-5100		
602	Dir, Night Vision & Electro-Optics Ctr CECCM ATTN: AMSEL-NV-D		
001	Fort Belvoir, VA 22060-5677		