

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

2

AD-A230 966

Information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and reviewing the collection of information, sending comments regarding this burden estimate or any other aspect of this collection of information, including this burden estimate, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Avenue, Washington, DC 20503, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

2. REPORT DATE October 1990		3. REPORT TYPE AND DATES COVERED Final 15 Aug 87 - 14 Aug 90	
4. TITLE AND SUBTITLE Synthesis, Structure and Properties of Segmented Polyurethanes		5. FUNDING NUMBERS DAAL03-87-K-0075	
6. AUTHOR(S) William J. MacKnight			
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Univ. of Massachusetts Amherst, MA 01003		8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) U. S. Army Research Office P. O. Box 12211 Research Triangle Park, NC 27709-2211		10. SPONSORING / MONITORING AGENCY REPORT NUMBER ARO 23941.3-CH	
11. SUPPLEMENTARY NOTES The view, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy, or decision, unless so designated by other documentation.			
12a. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution unlimited.		12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The effect of the introduction of mesogenic groups on the properties and structure of segmented polyurethanes was investigated. The objectives were to determine to what extent the phase behavior of such polyurethanes is controlled by the phase behavior of the mesogen and the effect of structural considerations such as hydrogen bonding and asymmetric placement of methyl groups on the phase behavior. A summary of the most important results appears in the final report.			
14. SUBJECT TERMS Segmented Polyurethanes, Polyurethanes, Hydrogen Bonding		15. NUMBER OF PAGES 4	
		16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL

DTIC
ELECTE
JAN 15 1991
S B D

SYNTHESIS, STRUCTURE AND PROPERTIES
OF SEGMENTED POLYURETHANES

FINAL REPORT

WILLIAM J. MACKNIGHT

OCTOBER 31, 1990

U.S. ARMY RESEARCH OFFICE
CONTRACT DAAL 03-87-K0075

UNIVERSITY OF MASSACHUSETTS
POLYMER SCIENCE AND ENGINEERING
AMHERST, MASSACHUSETTS 01003


APPROVED FOR PUBLIC RELEASE;
DISTRIBUTION UNLIMITED

A. Statement of the Problem

The effect of the introduction of mesogenic groups on the properties and structure of segmented polyurethanes was investigated. The objectives were to determine to what extent the phase behavior of such polyurethanes is controlled by the phase behavior of the mesogen and the effect of structural considerations such as hydrogen bonding and asymmetric placement of methyl groups on the phase behavior.


B. Summary of the Most Important Results

A series of polyurethanes containing the mesogenic diol, BHHBP, was synthesized

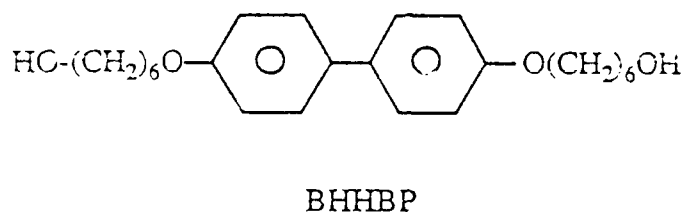

BHHBP was itself characterized with regard to its thermal and morphological behavior. The major findings of this research may be summarized as follows:

- (1) BHHBP forms a crystal phase which melts to produce a highly ordered smectic phase in which the molecules are tilted at 45° - 55° in the smectic layers.
- (2) A polyurethane synthesized from 2,4 toluene diisocyanate and BHHBP having the repeat unit

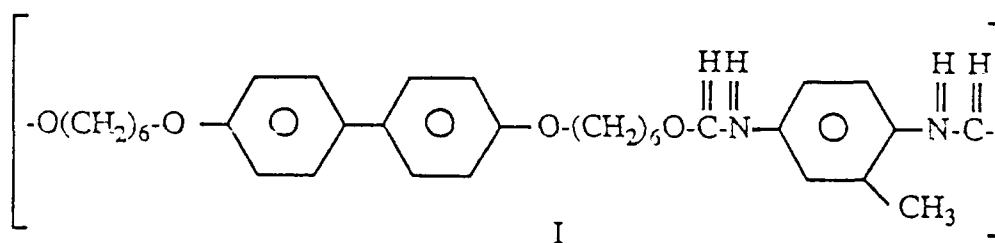

exhibited no thermodynamically stable mesophase. An evanescent mesophase can be produced on cooling from the isotropic melt. Its morphology can then be preserved by quick quenching the polymer below its glass transition temperature. On the basis of X-ray analysis, this mesophase is also of the smectic type with the molecules tilted in the smectic layers in a similar fashion to BHHBP itself. Polyurethane I forms a stable three dimensional crystalline phase.

- (3) A polyurethane identical in structure to I, but with the N-H groups replaced by N-CH₃ groups, exhibits a stable smectic mesophase, again similar in structure to that in BHHBP. This polymer does not crystallize under any experimental conditions.
- (4) A series of segmented polyurethanes with poly(tetramethylene oxide) soft segments and hard segments built up from BHHBP and either 2,4 toluene diisocyanate or "Hylene W". (dicyclohexane methane diisocyanate) was prepared. Preliminary results indicate that their mechanical properties are determined by the ability of the soft segment to crystallize under extension and their overall molecular weights. Only preliminary data are available concerning the morphology of the hard segment phase.
- (5) The kinetics of microphase separation in model segmented polyurethanes based on poly(tetramethylene oxide) and diphenylmethane diisocyanate with butane diol as a chain extender could be followed by observing spectral changes in the carbonyl stretching vibration region by Fourier Transform Infrared Spectroscopy. A model for this process based on the concepts of nucleation and growth analyzed by the method of Avrami was put forward.

C. List of Publications

1. Thermal and Rheological Properties of a Liquid-Crystalline Polyurethane
Macromolecules 1989 22, 1467.
2. Infrared and X-Ray Diffraction Studies of a Semi-Rigid Polyurethane
Macromolecules 1989 22, 551.
3. Spectroscopic Analysis of Phase Separation Kinetics in Model Polyurethanes
Macromolecules 1988 21, 270.
4. Development of Crystallinity in a Polyurethane Containing Mesogenic Units.
1. Morphology and Mechanisms
Macromolecules 1990 23, 3389.
5. Microstructure and Dynamics of a Mesogenic Diol
Liquid Crystals 1990 7, 838.
6. A Novel Synthesis of Mesogenic N-Methyl Polyurethanes and Demonstration of
the Effect of Hydrogen Bonding on Liquid Crystalline Properties
Polymer Preprints 1990 31, 486.

D. List of All Participating Scientific Personnel and Degrees Awarded

<u>Personnel</u>	<u>Degree</u>
Professor Shaw Ling Hsu	-
Professor Richard J. Farris	-
Professor William J. MacKnight	-
Doctor Enrique Valles	-
L. Anderson	Ph.D., Chemical Engineering
K. Antolin	-
Chen Ho Che	-
Elliot Douglas	M.A.
Chris Haak	M.A.
H.S. Lee	Ph.D.
S. Nitzsche	-
F. Papadimitrakopoulos	-
B. Reekmans	-
D.Y. Shi	-
K. Tung	-
D. Waldman	Ph.D.
Q. Wang	M.A.

Accession For	
NTIS GFA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By	
Distribution/	
Availability Codes	
Avail and/or	
Dist	Special
A-1	

