

SECURITY CLASSIFICATION OF THIS PAGE

## REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

1a R

U

2a S

2b C

AD-A239 170



1b. RESTRICTIVE MARKINGS

3. DISTRIBUTION/AVAILABILITY OF REPORT

Approval for public release; distribution unlimited

4. PERFORMING ORGANIZATION REPORT NUMBER(S)

Technical Report No. DU/DC/TR-21

5. MONITORING ORGANIZATION REPORT NUMBER(S)

6a. NAME OF PERFORMING ORGANIZATION

Department of Chemistry  
Duke University6b. OFFICE SYMBOL  
(If applicable)

7a. NAME OF MONITORING ORGANIZATION

Office of Naval Research

6c. ADDRESS (City, State, and ZIP Code)

Durham, NC 27706

7b. ADDRESS (City, State, and ZIP Code)

300 North Quincy Street  
Arlington, VA 22217-50008a. NAME OF FUNDING/SPONSORING  
ORGANIZATION

Office of Naval Research

8b. OFFICE SYMBOL  
(If applicable)

9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER

N00014-89-J-1545; R&amp;T Code 4135008

8c. ADDRESS (City, State, and ZIP Code)

800 North Quincy Street  
Arlington, VA 22217-5000

10. SOURCE OF FUNDING NUMBERS

PROGRAM  
ELEMENT NO.  
NRPROJECT  
NO.  
053TASK  
NO.  
841WORK UNIT  
ACCESSION NO.

11. TITLE (Include Security Classification)

SYNTHESIS AND STRUCTURAL CHARACTERIZATION OF ORGANOINDIUM-PHOSPHORUS COMPLEXES CONTAINING A FOUR-MEMBERED  
In-P-In-Cl OR In-P-In-P RING: CRYSTAL STRUCTURES OF  $(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}$  and  $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$ 

12. PERSONAL AUTHOR(S)

R.L. Wells, A.T. McPhail, and M.F. Self

13a. TYPE OF REPORT

Technical

13b. TIME COVERED

FROM \_\_\_\_\_ TO \_\_\_\_\_

14. DATE OF REPORT (Year, Month, Day)

1991-07-30

15. PAGE COUNT

25

16. SUPPLEMENTARY NOTATION

Accepted for publication in Organometallics.

17. COSATI CODES

| FIELD | GROUP | SUB-GROUP |
|-------|-------|-----------|
|       |       |           |
|       |       |           |
|       |       |           |

18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)

indium-phosphorus, synthesis, crystal structure,  
ring compounds

19. ABSTRACT (Continue on reverse if necessary and identify by block number)

See attached

91-06967



20. DISTRIBUTION/AVAILABILITY OF ABSTRACT

☒ UNCLASSIFIED/UNLIMITED ☐ SAME AS RPT ☐ DTIC USERS

21. ABSTRACT SECURITY CLASSIFICATION

Unclassified

22a. NAME OF RESPONSIBLE INDIVIDUAL

Richard L. Wells

22b. TELEPHONE (Include Area Code)

(919)-660-1541

22c. OFFICE SYMBOL

**Synthesis and Structural Characterization of  
Organoindium-Phosphorus Complexes Containing  
a Four-Membered  $\overline{\text{In-P-In-Cl}}$  or  $\overline{\text{In-P-In-P}}$  Ring:  
Crystal Structures of  
 $(\text{Me}_3\text{SiCH}_2)_2\overline{\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}}$  and  
 $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$**

Richard L. Wells\*, Andrew T. McPhail, and Mark F. Self

*Department of Chemistry, Paul M. Gross Chemical Laboratory,  
Duke University, Durham, NC 27706*

**ABSTRACT**

The first example of an  $\overline{\text{In-P-In-Cl}}$  ring containing compound,  $(\text{Me}_3\text{SiCH}_2)_2\overline{\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}}$  (1) was prepared by the reaction of  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  and  $(\text{Me}_3\text{Si})_3\text{P}$  in a 2:1 mole ratio. Similarly, the dimer containing an  $\overline{\text{In-P-In-P}}$  core,  $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$  (2) was prepared by reaction in a 1:1 mole ratio. X-ray crystallographic analyses showed the  $\overline{\text{In-P-In-Cl}}$  ring of 1 to be nonplanar while the  $\overline{\text{In-P-In-P}}$  ring of 2 is planar. Compound 1 belongs to the triclinic system, space group  $P\bar{1}$  ( $C_i^1$ ), with two molecules in a unit cell of dimensions:  $a = 12.581(1)$ ,  $b = 19.470(2)$ ,  $c = 9.643(1)$  Å,  $\alpha = 89.75(1)$ ,  $\beta = 112.91(1)$ ,  $\gamma = 100.68(1)^\circ$ . Compound 2 crystallizes in the orthorhombic system, space group  $Pbca(D_{2h}^{14})$ , with four molecules in a unit cell of dimensions:  $a = 12.782(2)$ ,  $b = 21.482(3)$ ,  $c = 18.651(3)$  Å. Compound 2 reacts with two equivalents of  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  to yield 1 as a major product, as evidenced by  $^1\text{H}$  and  $^{13}\text{C}\{^1\text{H}\}$  NMR and melting point data.

[Originally submitted to *Organometallics*; May 6, 1991]

[Revised submitted June 20, 1991]

**Synthesis and Structural Characterization of  
Organoindium-Phosphorus Complexes Containing  
a Four-Membered  $\overline{\text{In-P-In-Cl}}$  or  $\overline{\text{In-P-In-P}}$  Ring:**

**Crystal Structures of  
 $(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}$  and  
 $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$**

Richard L. Wells\*, Andrew T. McPhail, and Mark F. Self

*Department of Chemistry, Paul M. Gross Chemical Laboratory,*

*Duke University, Durham, NC 27706*

*(Received ..... , 1991)*

The first example of an  $\overline{\text{In-P-In-Cl}}$  ring containing compound,  $(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}$  (**1**) was prepared by the reaction of  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  and  $(\text{Me}_3\text{Si})_3\text{P}$  in a 2:1 mole ratio. Similarly, the dimer containing an  $\overline{\text{In-P-In-P}}$  core,  $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$  (**2**) was prepared

by reaction in a 1:1 mole ratio. X-ray crystallographic analyses showed the  $\overline{\text{In-P-In-Cl}}$  ring of **1** to be nonplanar while the  $\overline{\text{In-P-In-P}}$  ring of **2** is planar. Compound **1** belongs to the triclinic system, space group  $P\bar{1}$  ( $C_i^1$ ), with two molecules in a unit cell of dimensions:  $a = 12.581(1)$ ,  $b = 19.470(2)$ ,  $c = 9.643(1)$  Å,  $\alpha = 89.75(1)$ ,  $\beta = 112.91(1)$ ,  $\gamma = 100.68(1)^\circ$ . Compound **2** crystallizes in the orthorhombic system, space group  $Pbcn(D_{2h}^{14})$ , with four molecules in a unit cell of dimensions:  $a = 12.782(2)$ ,  $b = 21.482(3)$ ,  $c = 18.651(3)$  Å. Compound **2** reacts with two equivalents of  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  to yield **1** as a major product, as evidenced by  $^1\text{H}$  and  $^{13}\text{C}\{^1\text{H}\}$  NMR and melting point data.

### Introduction

Recently, there has been heightened interest concerning the production of crystalline nanometer size particles (nanocrystals) of semiconductor materials,<sup>1-4</sup> because they possess the important feature of exhibiting quantum confinement effects not seen in the bulk material.<sup>5-8</sup> Indeed, Alivisatos and coworkers recently reported the first proven example of the formation of nanocrystals of GaAs in polar organic solvents<sup>3</sup> utilizing a dehalosilylation reaction [viz.,  $\text{GaCl}_3$  with  $(\text{Me}_3\text{Si})_3\text{As}$ ] reported by us.<sup>9,10</sup> For some time, in our laboratory we have been applying this dehalosilylation methodology to the syntheses of novel III-V compounds<sup>11-17</sup> for, in part, possible conversion to III-V materials. Thus, reaction between an organogroup III halide and a silylarsine proceeds

readily and, in a number of cases, the core fragments of these complexes are composed of four-membered rings containing two group III metals bridged by either two arsenic atoms, or by one arsenic and one halogen atom. For example, compounds of the formula  $\overline{R_2MAs(SiMe_3)_2M(R)_2Cl}$  and  $[R_2MAs(SiMe_3)_2]_2$  ( $R = Ph^{13,14}$  or  $Me_3SiCH_2^{16}$ ,  $M = Ga$ ;  $R = Me_3SiCH_2^{17}$ ,  $M = In$ ) have been synthesized by us. In an effort to expand these fundamental investigations to include possible indium phosphide (InP) precursors, reactions were carried out with  $(Me_3SiCH_2)_2InCl$  and  $(Me_3Si)_3P$ . Herein, we report the isolation and crystal structure of the first example of a  $\overline{In-P-In-Cl}$  ring containing compound,  $(Me_3SiCH_2)_2\overline{InP(SiMe_3)_2In(CH_2SiMe_3)_2}Cl$  (**1**), as well as the recently reported dimer  $[(Me_3SiCH_2)_2InP(SiMe_3)_2]_2$  (**2**)<sup>4</sup>. The syntheses of compounds **1** and **2** from reactions of  $(Me_3SiCH_2)_2InCl$  and  $(Me_3Si)_3P$  in a 2:1 and 1:1 mole ratio, respectively, are described. Additionally, the conversion of **2** to **1** is reported.

## Experimental Section

**General Considerations.** All manipulations were performed using Schlenk techniques in a Vacuum/Atmospheres HE-43 Dri-Lab containing an argon atmosphere. Toluene was distilled from sodium/benzophenone ketyl under dry dinitrogen. Benzene- $d_6$  was dried over sodium/benzophenone ketyl and vacuum transferred from the flask containing the latter. Hexane was distilled over  $LiAlH_4$  under dry dinitrogen. Indium(III) chloride was purchased from Alfa Products, Ward

Hill, MA and used as received.  $(\text{Me}_3\text{Si})_3\text{P}$  was purchased from Quantum Design Inc., Austin, TX and was also used without further purification.  $(\text{Me}_3\text{SiCH}_2)_3\text{In}$  and  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$ <sup>18</sup> were prepared by literature procedures.  $^1\text{H}$ ,  $^{31}\text{P}$  and  $^{13}\text{C}$  NMR spectra were obtained on a Varian XL-300 (300.0, 121.4 and 75.4 MHz, respectively) spectrometer using 5 mm tubes.  $^1\text{H}$  and  $^{13}\text{C}$  spectra were referenced to TMS using the residual protons or carbons of deuterated benzene at  $\delta$  7.15 ppm and  $\delta$  128 ppm, respectively.  $^{31}\text{P}$  spectra were referenced externally to  $\text{H}_3\text{PO}_4$  at  $\delta$  0.00 ppm. NMR tubes were flame sealed under vacuum and all spectra were run in  $\text{C}_6\text{D}_6$ . All melting points were obtained from sealed capillaries with a Thomas-Hoover Uni-melt apparatus and are uncorrected. Crystals used in X-ray analyses were flame sealed under argon in 0.7 mm thin-walled glass capillaries. Elemental analyses were performed by E+R Microanalytical Laboratory, Inc., Corona, New York.

**Preparation of  $(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}$  (1).**

In the dry box,  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  (0.709 g, 2.18 mmol) in 15 mL of hexane and  $(\text{Me}_3\text{Si})_3\text{P}$  (0.273 g, 1.09 mmol) in 10 mL of hexane were combined in a 100-mL one-necked round-bottomed flask equipped with a Teflon valve and a micro-stirbar. After the resulting clear solution was removed from the box and stirred at room temperature for 24 h, the volatiles were removed *in vacuo* to yield a white residue. Dissolving the residue in approximately 3 mL of warm toluene followed by cooling to  $-15^\circ\text{C}$  for 5 days, afforded colorless crystals of **1** suitable for single-crystal X-ray analysis (0.657 g, 76% yield), m.p.  $60\text{--}63^\circ\text{C}$ . Anal. Calcd (Found) for  $\text{C}_{22}\text{H}_{62}\text{ClIn}_2\text{PSi}_6$ : C, 33.30 (33.54); H, 8.01 (7.74); P, 3.91 (3.70).  $^1\text{H}$  NMR:  $\delta$  0.16 (s, 8 H,  $\text{CH}_2$ ), 0.26 (s, 36 H,  $\text{SiMe}_3$ ), 0.33 (d, 18 H,  $\text{PSiMe}_3$  ( $J_{\text{P-H}} = 5.6$

Hz)).  $^{13}\text{C}$   $\{^1\text{H}\}$  NMR:  $\delta$  2.89 (s,  $\text{SiMe}_3$ ), 4.62 [d,  $\text{PSiMe}_3$  ( $J_{\text{P-C}} = 8.6$  Hz)], 7.28 [d,  $\text{CH}_2$  ( $J_{\text{P-C}} = 8.7$  Hz)].  $^{31}\text{P}$   $\{^1\text{H}\}$  NMR:  $\delta$  -218.99 (s)


**Preparation of  $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$  (2).** Reaction of  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  (0.628 g, 1.93 mmol) in 15 mL of hexane and  $(\text{Me}_3\text{Si})_3\text{P}$  (0.484 g, 1.93 mmol) in 10 mL of hexane was carried out in a fashion analogous to that for 1. After stirring the resulting solution at room temperature for 24 h, the volatiles were removed *in vacuo* to yield a white solid. The crude product was dissolved in approximately 20 mL of warm toluene and, upon cooling the solution for 48 h at  $-15^\circ\text{C}$ , a multitude of clear, colorless, and *extremely air-sensitive* crystals of 2 suitable for single-crystal X-ray analysis resulted. Removal of approximately 80% of the toluene by evaporation afforded a second crop of 2 (0.767 g total, 85% yield) [mp  $240^\circ\text{C}$  (lit<sup>4</sup> mp  $245^\circ\text{C}$ )]. Anal. Calcd (Found) for  $\text{C}_{28}\text{H}_{80}\text{In}_2\text{P}_2\text{Si}_8$ : C, 36.02 (36.23); H, 8.64 (8.21); P, 6.63 (6.42).  $^1\text{H}$  NMR:  $\delta$  0.20 (s, 8 H,  $\text{CH}_2$ ), 0.33 (s, 36 H,  $\text{SiMe}_3$ ), 0.46 [t, 36 H,  $\text{PSiMe}_3$  ( $J_{\text{P-H}} = 2.4$  Hz)].  $^{13}\text{C}$   $\{^1\text{H}\}$  NMR:  $\delta$  3.70 (s,  $\text{SiMe}_3$ ), 4.11 (s,  $\text{CH}_2$ ), 5.30 (t,  $\text{PSiMe}_3$  ( $J_{\text{P-C}} = 4.2$  Hz)).  $^{31}\text{P}$   $\{^1\text{H}\}$  NMR:  $\delta$  -227.36 (s).

**Reaction of 2 with  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$ .**  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  (12.5 mg, 0.038 mmol) and 2 (18.0 mg, 0.019 mmol) were combined in an NMR tube into which was vacuum distilled 0.75 mL of benzene- $\text{d}_6$ . After freezing the contents of the tube with liquid dinitrogen, the tube was flame-sealed and allowed to warm to ambient temperature. Upon standing for 3 h, the  $^1\text{H}$  NMR spectrum obtained for the mixture corresponded to that of an authentic sample of 1. The NMR tube was then opened in the dry box and the solvent evaporated to yield a colorless solid which melted at  $63^\circ\text{C}$ , a mp comparable to that found for authentic 1, *vide ante*.

**Structural Analyses of 1 and 2.** Crystallographic data and measurements are presented in Table I. Intensity data were corrected for the usual Lorentz and polarization effects; empirical absorption corrections were also applied. The structure of **1** was solved by the heavy-atom approach. Approximate coordinates for the indium atoms were derived from a Patterson map. The remaining non-hydrogen atoms were located in a series of weighted  $F_o$  and difference Fourier syntheses. For **2**, non-hydrogen atom coordinates of its isomorphous indium-arsenic analog<sup>17</sup> were used as initial values. Positional and thermal parameters (at first isotropic, then anisotropic) for both compounds were adjusted by means of several rounds of full-matrix least-squares calculations. Hydrogen atoms, except for those at the somewhat disordered C(32') and C(33') methyl groups in **1**, were included at their calculated positions during the final least-squares iterations which also included refinement of an extinction correction. Structure-factor calculations, neutral atom scattering factors and their anomalous dispersion corrections were taken from reference 19.


### Results and Discussion

The ambient temperature reaction of  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  and  $(\text{Me}_3\text{Si})_3\text{P}$  in a 2:1 mole ratio in hexane yields **1** via a dehalosilylation reaction (eq 1).

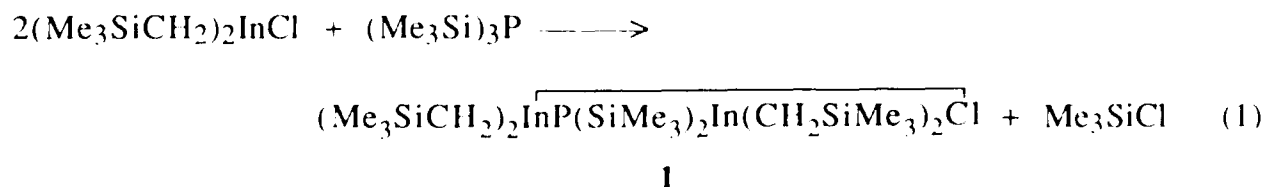

In that **1** contains an  $\overline{\text{In-P-In-Cl}}$  ring, it is the first reported example of a compound with the two indium atoms being bridged by both a phosphorus atom and a chlorine atom, and is yet another example of what we refer to as a "mixed-bridge" complex/compound.<sup>13-17</sup> Compound **1** is the phosphorus analog of our recently reported complex  $(\text{Me}_3\text{SiCH}_2)_2\overline{\text{InAs}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}}$  (**3**) which, as indicated, contains both an arsenic and chlorine bridge.<sup>17</sup> Interestingly, **3** undergoes gradual decomposition at ambient temperature, whereas **1** is quite stable for extended periods of time.

Reaction of  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  with  $(\text{Me}_3\text{Si})_3\text{P}$  in a 1:1 mole ratio afforded compound **2** (eq 2), the phosphorus analog of the dimer

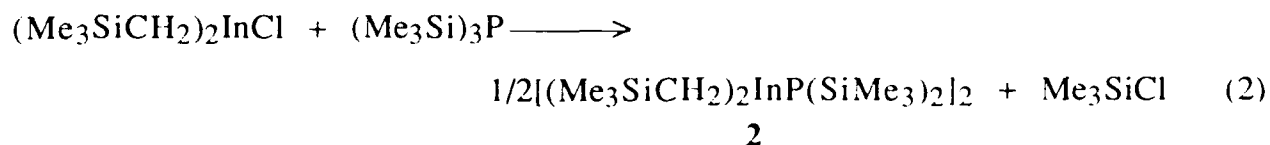


$[(\text{Me}_3\text{SiCH}_2)_2\text{InAs}(\text{SiMe}_3)_2]_2$  (**4**)<sup>17</sup>. Dimer **2** contains an  $\overline{\text{In-P-In-P}}$  core. Similarly, Theopold and coworkers also have isolated **2** and, while providing no detailed synthesis or complete structural characterization, it was reported that conversion of **2** to InP particles *via* an alcoholysis reaction was achieved.<sup>4</sup>

Previous studies in our laboratory have demonstrated quite clearly that dehalosilylation reactions between an organogallium or -indium halide and a silylarsine to form species containing metal-arsenic bonds occur

readily under mild conditions and in relatively high yields.<sup>11-17</sup> Although such reactions involving silylphosphines to form indium-phosphorus bonds have not been developed to the same extent, Barron and coworkers did report the isolation of InP from the thermolysis of the product obtained by the reaction of  $\text{InX}_3$  ( $\text{X} = \text{Cl}, \text{Br}$ ) with  $(\text{Me}_3\text{Si})_3\text{P}$  and, similarly, used a dehalosilylation reaction to form  $(\text{Me}_2\text{InPPh}_2)_2$ .<sup>20,21</sup>

The syntheses of **1** and **2** are clearly dependent upon the stoichiometry of the reagents used, and each is prepared in good yield. In the case of **1**, this is in marked contrast to its arsenic analog (*i.e.*, **3**), since the latter mixed-bridge complex was produced in only 16% yield. Both **1** and **2** are very soluble in nonpolar organic solvents, but **2** is significantly less soluble than **1**. Also, it is interesting to note that for the reactions involving  $(\text{Me}_3\text{SiCH}_2)_2\text{GaCl}$  with  $(\text{Me}_3\text{Si})_3\text{As}$  in either a 1:1 or 2:1 mole ratio, only the mixed bridge compound was observed as the major product.<sup>16</sup> Additionally, compound **1** can be produced easily by the reaction of **2** with  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$  in a 1:2 mole ratio (eq 3).

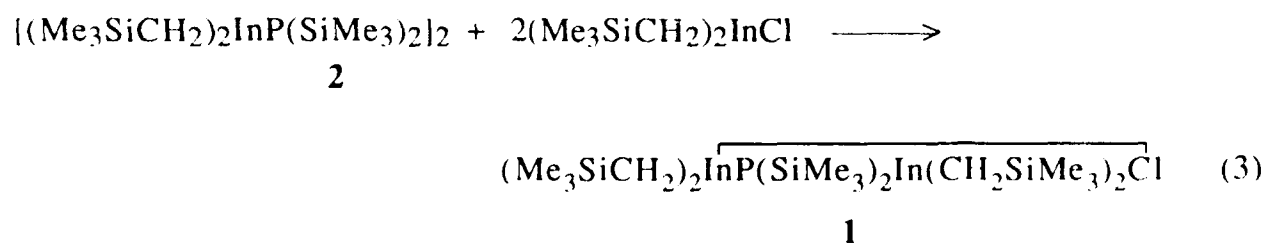

The  $^1\text{H}$  NMR spectra of both **1** and **2** show there is coupling of the  $^{31}\text{P}$  nuclei with the methyl protons of the adjacent trimethylsilyl groups. The former exhibits a doublet while the latter a triplet. As Douglas and Theopold noted<sup>4</sup>, the triplet resonance for **2** reveals the dimeric nature of

the complex in solution. Thus, it would follow that complex **1** should exhibit a doublet being that there is only one phosphorus atom in the ring. It is from the inherent differences between the two  $^1\text{H}$  NMR spectra that the conversion of **2** to **1** can be easily monitored from the reaction of **2** and additional  $(\text{Me}_3\text{SiCH}_2)_2\text{InCl}$ .

In the  $^{13}\text{C}$  NMR spectra, it is noteworthy that for both **1** and **2** coupling is again observed between the  $^{31}\text{P}$  nuclei and the adjacent trimethylsilyl groups. However, for complex **1**, coupling is also seen with the adjacent methylene protons in the (trimethylsilyl)methyl groups. As for the  $^{31}\text{P}$  NMR spectra, of **1** and **2**, each exhibits one sharp resonance indicating that each compound exist as a single species. This behavior for **2** differs substantially from that of  $[(\text{Me}_3\text{SiCH}_2)_2\text{InPPh}_2]_2$  which was shown to exist as an equilibrium mixture of monomer and dimer in solution.<sup>22</sup>

Crystals of **1** suitable for X-ray analysis were obtained by recrystallization from a toluene solution. Crystallographic data are summarized in Table I. Figure 1 presents an ORTEP diagram showing the atom numbering scheme for **1**. Table II lists the non-hydrogen atoms fractional coordinates and equivalent isotropic thermal parameters; selected bond lengths and angles are reported in Table IV.

Compound **1** crystallizes in the triclinic system with the two molecules in the unit cell occupying the general positions of the centrosymmetric space group  $P\bar{1}$ . It is of interest that the  $\overline{\text{In-P-In-Cl}}$  ring in **1** is distinctly non-planar, whereas in the As analog **3**, the As and Cl atoms lie on a crystallographic  $C_2$  symmetry axis and thus the

$\overline{\text{In-As-In-Cl}}$  ring is flat.<sup>17</sup> The mean of the In-Cl bond lengths [2.630(3), 2.611(2) Å] at 2.621 Å in **1** is virtually identical to the In-Cl distance of 2.619(2) Å in **3**. The Cl atom is displaced by 1.020 Å from the In-P-In' plane in **1** giving rise to a dihedral angle of 33.3(1)° between the In-P-In' and In-Cl-In' planes [mean endocyclic torsion angle about the ring bonds = 22.9(1)°], and thus the ring is considerably puckered. The departure from coplanarity in **1** aids in relieving non-bonded intramolecular steric overcrowding of the bulky ring substituents. These effects are more severe in **1** than **3** as a consequence of the shorter distances for bonds involving phosphorus [mean In-P = 2.603 Å, mean P-Si = 2.252 Å] in contrast to the longer In-As and As-Si distances of 2.677(1) Å and 2.356(2) Å, respectively, in **3**. The In-P-In', In-Cl-In' and mean P-In-Cl bond angles are 90.6(1), 89.8(1), and 85.1°, respectively.

Previous structural studies in our laboratory have shown that the Si-As-Si angle at 103.66(4)° in  $[(\text{Me}_3\text{Si})_2\text{AsGa}(\text{CH}_2\text{SiMe}_3)_2]_2$ <sup>16</sup> lies close to the essentially equal C-As-C angles of 104.3(2)° subtended at the ring As atoms in  $\{[(\text{Me}_3\text{SiCH}_2)_2\text{As}]_2\text{GaBr}\}_2$ <sup>12</sup> and 104.4(2)° in  $[(\text{Me}_3\text{SiCH}_2)_2\text{As-GaPh}_2]_2$ ,<sup>23</sup> thereby indicating that the  $\text{Me}_3\text{Si}$  and  $\text{Me}_3\text{SiCH}_2$  ring substituents have comparable steric demands. The mean C-In-C bond angle at 127.9° in **1** is similar to the C-In-C angle of 126.3(3)° in **3**, and, although steric effects may make some contribution to the very significant enlargement over tetrahedral (109.5°), the principal factors must be electronic in nature.

Recrystallization of **2** from toluene provided crystals suitable for an X-ray structural study. Crystal data are reported in Table 1 along with data collection and refinement parameters. An ORTEP diagram, with the

atom numbering scheme, is provided in Figure 2. Non-hydrogen atom fractional coordinates are listed in Table III; Table V contains selected bond lengths and angles.

Compound **2** crystallizes in the orthorhombic system, space group *Pbcn*, with four formula units per unit cell. It is isomorphous with  $[(\text{Me}_3\text{SiCH}_2)_2\text{InAs}(\text{SiMe}_3)_2]_2$  (**4**)<sup>17</sup> as well as  $[(\text{Me}_3\text{SiCH}_2)_2\text{GaAs}(\text{SiMe}_3)_2]_2$ ,<sup>16</sup> and thus accordingly it also lies on a crystallographic  $C_2$  axis which passes through the group III centres. The four-membered ring is required by symmetry to be strictly planar. The In-P bonds [2.656(2), 2.654(2) Å] are essentially equal and their mean at 2.655 Å is significantly greater ( $\Delta = 0.051$  Å) than the mean of 2.603 Å in **1**; a similar difference of 0.045 Å, and in the same sense, is found between the In-As bonds of **3** and **4**, indicating that group III-group V bond strain is greater in the dimers than in the mixed-bridged species. The bond angle pattern in the ring P-In-P << In-P-In ( $\Delta = 7.2^\circ$ ) in **2** is also similar to that in the As analog **4** ( $\Delta = 9.3^\circ$ ). The mean C-In-C angle at  $123.2^\circ$  in **2** is slightly smaller than that of  $125.4^\circ$  in **4**; the Si-P-Si angles [ $105.2(2)^\circ$  in **2**,  $105.4(2)^\circ$  in **4**] are equal.

The literature contains numerous examples of compounds containing  $\overline{\text{In-P-In-P}}$  units.<sup>2,4,21,22,24,25</sup> However, only two such structures contain similar alkyl substituents (i.e.,  $\text{Me}_3\text{SiCH}_2$  or  $\text{Me}_3\text{Si}$ ) and therefore warrant comparison with **2**. As was previously noted, Beachley *et al* reported the structure of  $[(\text{Me}_3\text{SiCH}_2)_2\text{InPPh}_2]_2$  (**5**).<sup>22</sup> Compound **5** was prepared *via* two routes: an alkane elimination involving  $\text{HPPh}_2$  and  $\text{In}(\text{Me}_3\text{SiCH}_2)_3$  or a salt elimination between  $\text{KPPh}_2$  and  $(\text{Me}_3\text{SiCH}_2)_2\text{InBr}$ . As found for **2**, compound **5** contains a planar  $\overline{\text{In-P-In-P}}$  core and the average In-P

length of 2.65(1) Å compares favorably to that of **2** (*vide ante*). Conversely, the mean In-P-In and P-In-P bond angles in **5** differ significantly from those in **2** [97.49(11) and 82.52(10)° for **5**, and 93.6(1) and 86.4(1)° for **2**, respectively]. These differences can be explained sterically where less demanding phenyl groups allow the In-P-In angle to open up somewhat. It then follows that with these smaller phenyl substituents, the Me<sub>3</sub>SiCH<sub>2</sub> groups are able to move further apart, thus causing the P-In-P angle to decrease accordingly.

The only other published structural example of a compound containing an  $\overline{\text{In-P-In-P}}$  ring with trimethylsilyl substituents on phosphorus was first reported in 1989 and then again in 1991 by Theopold and coworkers<sup>2,4</sup>. This compound, [Cp\*(Cl)InP(SiMe<sub>3</sub>)<sub>2</sub>]<sub>2</sub> (**6**) (Cp\* = C<sub>5</sub>Me<sub>5</sub>), is apparently produced by three different pathways: the novel reaction of Cp\*<sub>2</sub>InCl with LiP(SiMe<sub>3</sub>)<sub>2</sub> to eliminate LiCp\*<sub>2</sub>, and by reaction of Cp\*InCl<sub>2</sub> with either LiP(SiMe<sub>3</sub>)<sub>2</sub> or P(SiMe<sub>3</sub>)<sub>3</sub> to yield LiCl and Me<sub>3</sub>SiCl, respectively<sup>4</sup>. Compound **6** has an average In-P bond length of 2.63(4) Å which is slightly shorter than those in **2**, and it contains In-P-In and P-In-P bond angles [92.2(1) and 87.8(1)°, respectively] which are quite similar to those found in **2** (*vide ante*).

### Conclusions

The work described here demonstrates that, in addition to being a facile route to compounds containing the  $\overline{\text{In-P-In-P}}$  ring, the use of the dehalosilylation methodology allows for the ready preparation of the  $\overline{\text{In-P-In-Cl}}$  moiety. As has been shown by Theopold and coworkers<sup>2,4</sup>,

organoindium compounds containing the  $(\text{Me}_3\text{Si})_2\text{P}$  group can be converted to InP by alcoholysis and, in the case of **2**, there is evidence for nanometer size particles being formed<sup>4</sup>. Thus, mixed-bridge complex **1** and some of its derivatives appear to be likely single-source InP precursors. In addition, the ease with which dimer **2** can be converted to the mixed bridge species **1**, underscores the possible synthetic usefulness of this type of complex to the preparation of other related species. We will use this investigation as a another benchmark for future studies into the formation of suitable precursors to InP and other In containing III-V alloys.

**Acknowledgment.** The financial support for this work by the Office of Naval Research is gratefully acknowledged.

**Supplementary Material Available:** Tables of hydrogen atom coordinates and isotropic thermal parameters, anisotropic temperature factors, complete lists of interatomic distances and angles, including torsion angles for **1** and **2**, and equations of least-squares planes through groups of atoms for **1** (13 pages); a listing of observed and calculated structure amplitudes for **1** and **2** (42 pages). Ordering information is given on any current masthead page.

## References

- (1) Byrne, E. K.; Parkanyi, L.; Theopold, K. H. *Science* **1988**, *241*, 332.
- (2) Byrne, E. K.; Douglas, T.; Theopold, K. H. *Mat. Res. Symp. Proc.* **1989**, *131*, 59.
- (3) Olshavsky, M. A.; Goldstein, A. N.; Alivisatos, A. P. *J. Am. Chem. Soc.* **1990**, *112*, 9438.
- (4) Douglas, T.; Theopold, K. H. *Inorg. Chem.* **1991**, *30*, 596.
- (5) Glass, A. M. *Science* **1987**, *235*, 1003.
- (6) Alivisatos, A. P.; Harris, T. D.; Brus, L. E.; Jayaraman, A. J. *J. Chem. Phys.* **1988**, *89*, 5979.
- (7) Shiang, J. J.; Goldstein, A. N.; Alivisatos, A. P. *J. Chem. Phys.* **1990**, *92*, 3232.
- (8) Koch, S. W. *Phys. Bl.* **1990**, *46*, 167.
- (9) Wells, R. L.; Pitt, C. G.; McPhail, A. T.; Purdy, A. P.; Shafieezad, S.; Hallock, R. B. *Chemistry of Materials* **1989**, *1*, 4.
- (10) Wells, R. L.; Pitt, C. G.; McPhail, A. T.; Purdy, A. P.; Shafieezad, S.; Hallock, R. B. *Materials Research Society Symposium Proceedings* **1989**, *131*, 45.
- (11) Pitt, C. G.; Purdy, A. P.; Higa, K. T.; Wells, R. L. *Organometallics* **1986**, *5*, 1266.
- (12) Purdy, A. P.; Wells, R. L.; McPhail, A. T.; Pitt, C. G. *Organometallics* **1987**, *6*, 2099.
- (13) Wells, R. L.; Holley, W. K.; Shafieezad, S.; McPhail, A. T.; Pitt, C. G. *Phosphorus, Sulfur, Silicon and Relat. Elem.* **1989**, *41*, 15.
- (14) Holley, W. K.; Wells, R. L.; Shafieezad, S.; McPhail, A. T.; Pitt, C. G. *J. Organomet. Chem.* **1990**, *381*, 15.

- (15) Holley, W. K.; Pasterczyk, J. W.; Pitt, C. G.; Wells, R. L. *Heteroatom Chem.* **1990**, *1*, 475.
- (16) Wells, R. L.; Pasterczyk, J. W.; McPhail, A. T.; Johansen, J. D.; Alvanipour, A. *J. Organomet. Chem.* **1991**, *407*, 17.
- (17) Wells, R. L.; Jones, L. J.; McPhail, A. T.; Alvanipour, A. *Organometallics*, in press.
- (18) Beachley, O. T.; Rusinko, R. N. *Inorg. Chem.* **1979**, *18*, 1966.
- (19) *International Tables for X-ray Crystallography*; The Kynoch Press, Birmingham, England, 1974, Vol IV.
- (20) Healy, M. D.; Laibinis, P. E.; Stupik, P. D.; Barron, A. R. *J. Chem. Soc., Chem. Commun.* **1989**, 359.
- (21) Arif, A. M.; Barron, A. R. *Polyhedron* **1988**, *7*, 2091.
- (22) Beachley, O. T.; Kopasz, J. P.; Zhang, H.; Hunter, W. E.; Atwood, J. L. *J. Organomet. Chem.* **1987**, *325*, 69.
- (23) Wells, R. L.; Purdy, A. P.; McPhail, A. T.; Pitt, C. G., *J. Organomet. Chem.* **1986**, *308*, 281.
- (24) Alcock, N. W.; Degnan, I. A.; Wallbridge, M. G. H.; Powell, H. R.; McPartlin, M.; Sheldrick, G. M. *J. Organomet. Chem.* **1989**, *361*, C33.
- (25) Aitchison, K. A.; Backer-Dirks, J. D.; Bradley, D. C.; Faktor, M. M.; Frigo, D. M.; Hursthouse, M. B.; Hussain, B.; Short, R. L. *J. Organomet. Chem.* **1989**, *366*, 11.

Captions to Figures

Figure 1. ORTEP diagram (40% probability ellipsoids) showing the structure and atom numbering scheme of  $(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}$  (1); hydrogen atoms have been omitted for clarity.

Figure 2. ORTEP diagram (40% probability ellipsoids) showing the structure and atom numbering scheme of  $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$  (2); hydrogen atoms have been omitted for clarity.

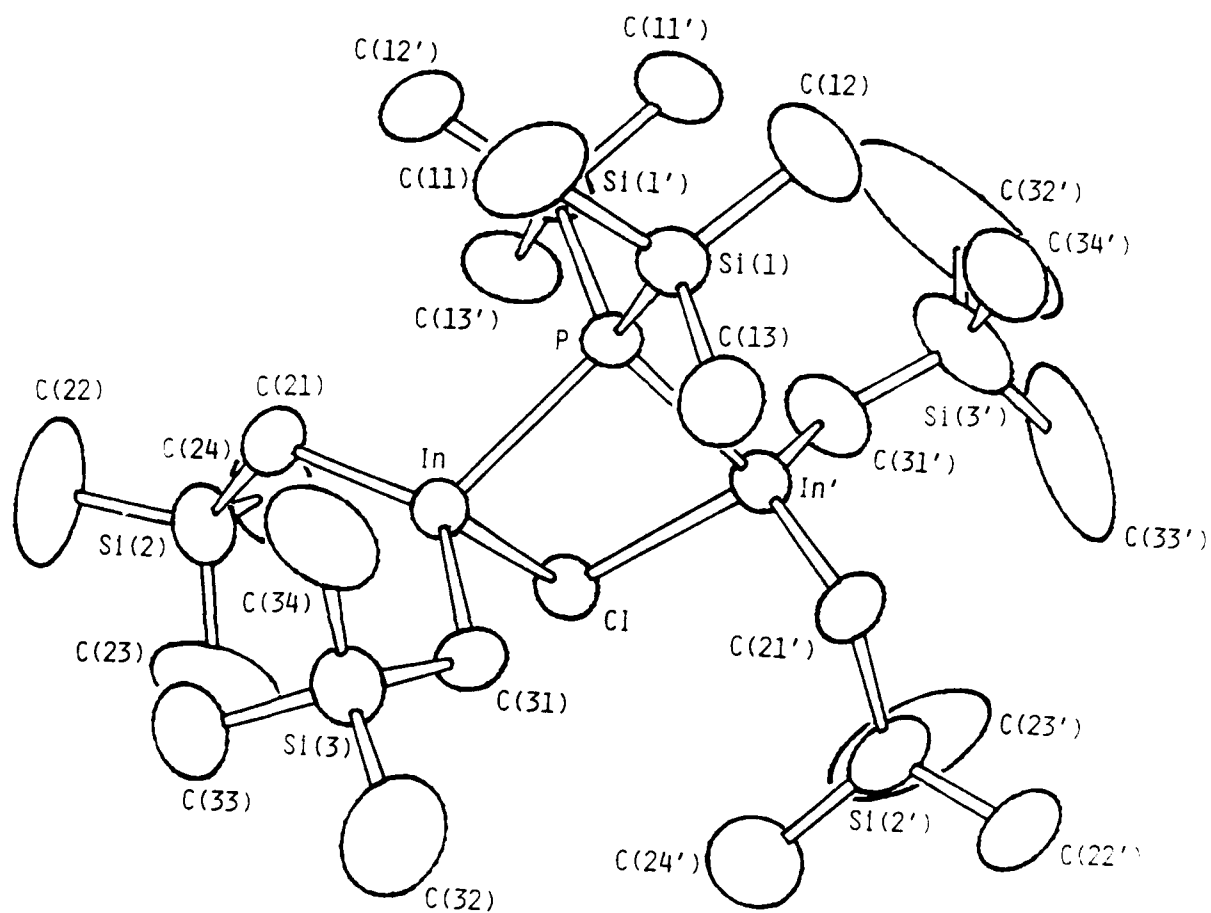


Figure 1

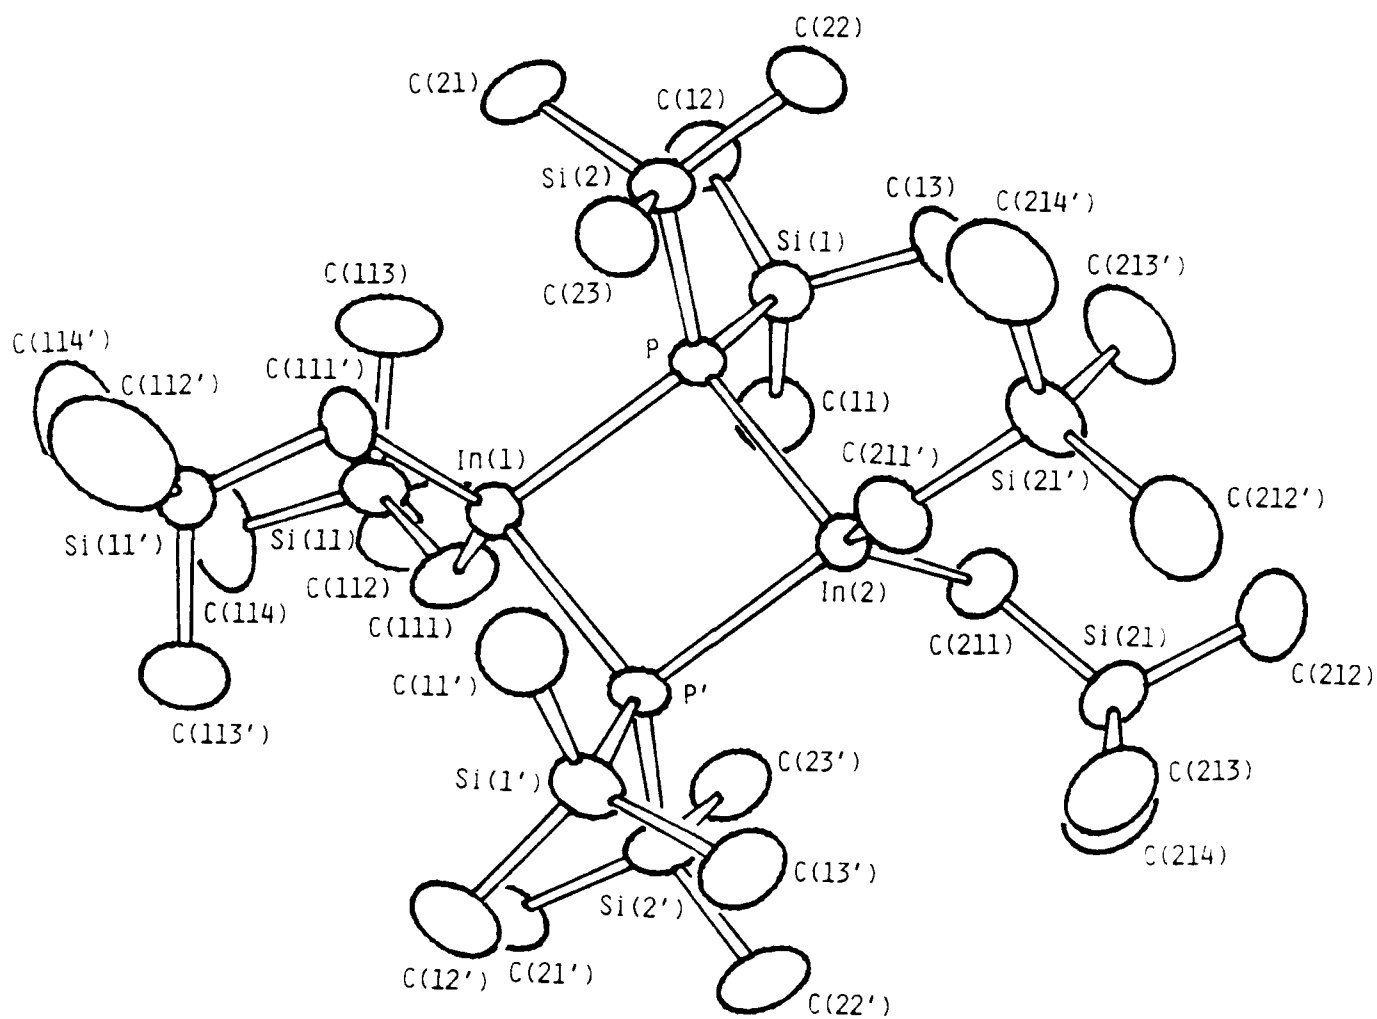


Figure 2

Table I. Crystallographic Data and Measurements<sup>a</sup> for $(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}$  (1) and $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$  (2)

|                                             | 1                                                     | 2                                                            |
|---------------------------------------------|-------------------------------------------------------|--------------------------------------------------------------|
| molecular formula                           | $\text{C}_{22}\text{H}_{62}\text{PClIn}_2\text{Si}_6$ | $\text{C}_{28}\text{H}_{80}\text{P}_2\text{In}_2\text{Si}_8$ |
| formula weight                              | 791.32                                                | 933.23                                                       |
| crystal system                              | triclinic                                             | orthorhombic                                                 |
| space group                                 | $P\bar{1}(C_i^1)$                                     | $Pbca(D_{2h}^{14})$                                          |
| $a$ , Å                                     | 12.581(1)                                             | 12.782(2)                                                    |
| $b$ , Å                                     | 19.470(2)                                             | 21.482(3)                                                    |
| $c$ , Å                                     | 9.643(1)                                              | 18.651(3)                                                    |
| $\alpha$ , deg                              | 89.75(1)                                              | 90.00(-)                                                     |
| $\beta$ , deg                               | 112.91(1)                                             | 90.00(-)                                                     |
| $\gamma$ , deg                              | 100.68(9)                                             | 90.00(-)                                                     |
| no. of orient. refls; $\theta$ , deg, range | 25; 27-35                                             | 25; 35-40                                                    |
| $V$ , Å <sup>3</sup>                        | 2132.1(9)                                             | 5121(2)                                                      |
| $Z$                                         | 2                                                     | 4                                                            |
| $D_{\text{calcd}}$ , g cm <sup>-3</sup>     | 1.233                                                 | 1.210                                                        |
| temp, °C                                    | 23                                                    | 23                                                           |
| crystal dimensions, mm                      | 0.14 x 0.19 x 0.45                                    | 0.32 x 0.40 x 0.44                                           |
| $T_{\text{max}}:T_{\text{min}}$             | 1.00:0.55                                             | 1.00:0.46                                                    |
| radiation (wavelength)                      | Cu- $K\alpha$ (1.5418 Å)                              | Cu- $K\alpha$ (1.5418 Å)                                     |
| $\mu$ , cm <sup>-1</sup>                    | 115.2                                                 | 99.2                                                         |
| scan type                                   | $\omega$ -2 $\theta$                                  | $\omega$ -2 $\theta$                                         |

Table I. (continued)

|                                                |                         |                         |
|------------------------------------------------|-------------------------|-------------------------|
| scan width, deg                                | $0.80 + 0.14\tan\theta$ | $0.80 + 0.14\tan\theta$ |
| $\theta_{\max}$ , deg                          | 65                      | 75                      |
| intensity control rflns                        | 222,312,151,141         | 115,223,223,115         |
| variation; repeat time, h                      | <2%; 2                  | <1%; 2                  |
| no of rflns recorded                           | 8061 (+h,+k,+l)         | 5261 (+h,+k,+l)         |
| no of rflns retained, $I > 3.0\sigma(I)$       | 4077                    | 2081                    |
| no of parameters refined                       | 290                     | 183                     |
| extinction correction                          | $6.6(5) \times 10^{-7}$ | $2.8(1) \times 10^{-7}$ |
| R, $R_w^b$                                     | 0.046, 0.058            | 0.047, 0.062            |
| goodness-of-fit <sup>c</sup>                   | 1.16                    | 1.15                    |
| max shift;<br>esd in final least-squares cycle | 0.02                    | 0.02                    |
| final $\Delta\rho(e/\text{\AA}^3)$ max; min    | 0.82; -0.58             | 0.79; -1.12             |

<sup>a</sup>An Enraf-Nonius CAD-4 diffractometer equipped with a graphite monochromator was used for all measurements. Crystallographic calculations were performed on PDP11/44 and MicroVAX computers by use of the Enraf-Nonius Structure Determination Package (SDP).

<sup>b</sup> $R = \sum ||F_o| - |F_c|| / \sum |F_o|$ ;  $R_w = [\sum w (|F_o| - |F_c|)^2 / \sum w |F_o|^2]^{1/2}$ ;  $\sum w \Delta^2 [w = 1/\sigma^2(|F_o|), \Delta = (|F_o| - |F_c|)]$  was minimized.

<sup>c</sup>Goodness-of-fit =  $[\sum w \Delta^2 / (N_{\text{observations}} - N_{\text{parameters}})]^{1/2}$ .

Table II. Non-hydrogen Atom Fractional Coordinates and Equivalent Isotropic Thermal Parameters for 1, with Estimated Standard Deviations in Parentheses.

| atom   | <i>x</i>    | <i>y</i>   | <i>z</i>    | <i>B</i> <sub>eq</sub> (Å <sup>2</sup> ) |
|--------|-------------|------------|-------------|------------------------------------------|
| P      | 0.0584(2)   | 0.3070(1)  | 0.3304(2)   | 3.92(4)                                  |
| In     | -0.11679(4) | 0.20821(3) | 0.16724(6)  | 4.15(1)                                  |
| In'    | 0.19445(4)  | 0.26442(3) | 0.21818(6)  | 4.47(1)                                  |
| Cl     | -0.0007(2)  | 0.2094(1)  | -0.0084(2)  | 5.04(5)                                  |
| Si(1)  | 0.1128(2)   | 0.3083(1)  | 0.5825(3)   | 4.83(6)                                  |
| Si(2)  | -0.3588(2)  | 0.2204(2)  | -0.1570(3)  | 6.81(8)                                  |
| Si(3)  | -0.2105(2)  | 0.0633(2)  | 0.3245(3)   | 6.36(7)                                  |
| Si(1') | 0.0193(2)   | 0.4111(1)  | 0.2456(3)   | 5.75(7)                                  |
| Si(2') | 0.2914(3)   | 0.1105(2)  | 0.2264(3)   | 7.89(8)                                  |
| Si(3') | 0.4265(3)   | 0.3903(3)  | 0.2248(4)   | 13.1(1)                                  |
| C(11)  | -0.0083(9)  | 0.3288(7)  | 0.6312(11)  | 9.5(3)                                   |
| C(12)  | 0.2509(10)  | 0.3762(7)  | 0.6785(12)  | 8.9(4)                                   |
| C(13)  | 0.1390(9)   | 0.2204(5)  | 0.6403(10)  | 6.7(3)                                   |
| C(11') | 0.1511(10)  | 0.4826(5)  | 0.3324(13)  | 8.1(4)                                   |
| C(12') | -0.1017(9)  | 0.4329(6)  | 0.2911(14)  | 8.8(4)                                   |
| C(13') | -0.0270(11) | 0.4027(5)  | 0.0352(12)  | 8.4(4)                                   |
| C(21)  | -0.2749(7)  | 0.2476(5)  | 0.0485(9)   | 5.4(2)                                   |
| C(22)  | -0.5130(11) | 0.2282(13) | -0.2145(15) | 16.8(7)                                  |
| C(23)  | -0.3598(17) | 0.1286(8)  | -0.2013(16) | 14.2(7)                                  |
| C(24)  | -0.2956(11) | 0.2733(8)  | -0.2742(13) | 10.6(5)                                  |
| C(31)  | -0.0993(7)  | 0.1067(4)  | 0.2547(9)   | 5.1(2)                                   |
| C(32)  | -0.1781(11) | -0.0234(7) | 0.3926(16)  | 12.3(4)                                  |
| C(33)  | -0.3602(9)  | 0.0426(7)  | 0.1638(15)  | 9.3(4)                                   |
| C(34)  | -0.2183(11) | 0.1196(8)  | 0.4709(14)  | 12.5(4)                                  |
| C(21') | 0.2608(7)   | 0.1768(5)  | 0.3336(10)  | 6.0(2)                                   |
| C(22') | 0.4006(9)   | 0.0631(6)  | 0.3554(14)  | 9.3(4)                                   |
| C(23') | 0.3289(14)  | 0.1453(9)  | 0.0734(15)  | 19.9(5)                                  |

Table II. (continued)

| atom   | $x$        | $y$        | $z$        | $B_{\text{eq}}(\text{\AA}^2)$ |
|--------|------------|------------|------------|-------------------------------|
| C(24') | 0.1528(15) | 0.0437(9)  | 0.1306(20) | 18.7(6)                       |
| C(31') | 0.2801(8)  | 0.3410(6)  | 0.1140(10) | 8.0(3)                        |
| C(32') | 0.4452(22) | 0.4814(12) | 0.1737(23) | 40.5(8)                       |
| C(33') | 0.5314(13) | 0.3414(16) | 0.2033(25) | 48(1)                         |
| C(34') | 0.4576(12) | 0.3963(8)  | 0.4283(17) | 11.5(5)                       |

**Table III. Non-hydrogen Atom Fractional Coordinates and Equivalent Isotropic Thermal Parameters for 2, with Estimated Standard Deviations in Parentheses.**

| atom   | <i>x</i>               | <i>y</i>   | <i>z</i>               | <i>B</i> <sub>eq</sub> (Å <sup>2</sup> ) |
|--------|------------------------|------------|------------------------|------------------------------------------|
| P      | 0.1411(2)              | 0.1854(1)  | 0.2382(1)              | 3.01(4)                                  |
| In(1)  | 0.0000(-) <sup>a</sup> | 0.27559(3) | 0.2500(-) <sup>a</sup> | 3.23(1)                                  |
| In(2)  | 0.0000(-) <sup>a</sup> | 0.09537(3) | 0.2500(-) <sup>a</sup> | 3.04(1)                                  |
| Si(1)  | 0.2355(2)              | 0.1746(1)  | 0.1368(2)              | 4.47(6)                                  |
| Si(2)  | 0.2589(2)              | 0.1895(2)  | 0.3280(2)              | 4.53(6)                                  |
| Si(11) | 0.0388(3)              | 0.3885(1)  | 0.1151(2)              | 4.45(6)                                  |
| Si(21) | -0.0846(3)             | -0.0219(1) | 0.1310(2)              | 5.20(7)                                  |
| C(11)  | 0.1468(12)             | 0.1906(6)  | 0.0608(6)              | 6.3(3)                                   |
| C(12)  | 0.3503(10)             | 0.2281(6)  | 0.1338(8)              | 7.0(3)                                   |
| C(13)  | 0.2859(10)             | 0.0928(6)  | 0.1295(7)              | 6.3(3)                                   |
| C(21)  | 0.3309(10)             | 0.2656(6)  | 0.3285(8)              | 7.3(4)                                   |
| C(22)  | 0.3581(10)             | 0.1257(6)  | 0.3195(7)              | 6.8(3)                                   |
| C(23)  | 0.1871(10)             | 0.1812(6)  | 0.4157(6)              | 6.2(3)                                   |
| C(111) | -0.0392(10)            | 0.3241(5)  | 0.1513(6)              | 5.7(3)                                   |
| C(112) | 0.0290(16)             | 0.3892(10) | 0.0162(10)             | 14.8(8)                                  |
| C(113) | 0.1804(12)             | 0.3845(8)  | 0.1387(11)             | 10.6(5)                                  |
| C(114) | -0.0162(19)            | 0.4620(6)  | 0.1416(16)             | 16.7(9)                                  |
| C(211) | -0.0028(10)            | 0.0476(4)  | 0.1472(16)             | 4.6(2)                                   |
| C(212) | -0.0011(13)            | -0.0911(6) | -0.1090(11)            | 9.7(5)                                   |
| C(213) | -0.1740(12)            | -0.0407(6) | 0.2065(8)              | 8.1(4)                                   |
| C(214) | -0.1701(13)            | -0.0114(8) | 0.0523(9)              | 9.3(5)                                   |

<sup>a</sup> Fixed by symmetry.

Table IV. Selected Bond Distances ( $\text{\AA}$ ) and Angles (deg) for 1, with Estimated Standard Deviations in Parentheses.

| Bond Lengths   |          |                   |          |
|----------------|----------|-------------------|----------|
| P-In           | 2.605(2) | In'-Cl            | 2.611(2) |
| P-In'          | 2.601(3) | In-C(21)          | 2.15(1)  |
| P-Si(1)        | 2.253(3) | In'-C(21')        | 2.15(1)  |
| P-Si(1')       | 2.250(3) | In-C(31)          | 2.16(1)  |
| In-Cl          | 2.630(3) | In'-C(31')        | 2.15(1)  |
| Bond Angles    |          |                   |          |
| In-P-In'       | 90.6(1)  | Cl-In-C(31)       | 99.5(3)  |
| In-P-Si(1)     | 116.8(1) | Cl-In'-C(31')     | 102.4(2) |
| In-P-Si(1')    | 108.8(1) | C(21)-In-C(31)    | 128.8(3) |
| In'-P-Si(1)    | 117.7(1) | C(21')-In'-C(31') | 126.9(4) |
| In'-P-Si(1')   | 110.2(1) | In-Cl-In'         | 89.8(1)  |
| Si(1)-P-Si(1') | 111.1(1) | P-Si(1)-C(11)     | 109.2(3) |
| P-In-Cl        | 84.9(1)  | P-Si(1')-C(11')   | 111.2(3) |
| P-In'-Cl       | 85.3(1)  | P-Si(1)-C(12)     | 109.6(4) |
| P-In-C(21)     | 112.2(2) | P-Si(1')-C(12')   | 110.5(4) |
| P-In'-C(21')   | 110.1(3) | P-Si(1)-C(13)     | 107.8(3) |
| P-In-C(31)     | 112.2(2) | P-Si(1')-C(13')   | 106.9(3) |
| P-In'-C(31')   | 116.6(3) | In-C(21)-Si(2)    | 118.3(5) |
| Cl-In-C(21)    | 108.7(3) | In-C(21')-Si(2')  | 118.1(5) |
| Cl-In'-C(21')  | 105.3(2) | In-C(31)-Si(3)    | 117.5(5) |
|                |          | In-C(31')-Si(3')  | 119.5(5) |

**Table V. Selected Bond Distances (Å) and Angles (deg) for 2,  
with Estimated Standard Deviations in Parentheses.**

---

| Bond Lengths |          |              |           |
|--------------|----------|--------------|-----------|
| P-In(1)      | 2.656(2) | In(1)-C(111) | 2.174(11) |
| P-In(2)      | 2.654(2) | In(2)-C(211) | 2.175(9)  |
| P-Si(1)      | 2.255(4) |              |           |
| P-Si(2)      | 2.254(4) |              |           |

| Bond Angles    |          |                      |          |
|----------------|----------|----------------------|----------|
| In(1)-P-In(2)  | 93.6(1)  | P-Si(2)-C(22)        | 111.1(4) |
| In(1)-P-Si(1)  | 120.5(1) | P-Si(2)-C(23)        | 108.4(4) |
| In(1)-P-Si(2)  | 111.3(1) | P-In(1)-C(111')      | 105.3(3) |
| In(2)-P-Si(1)  | 111.0(1) | P-In(1)-(P')         | 86.3(1)  |
| In(2)-P-Si(2)  | 114.8(1) | C(111)-In(1)-C(111') | 122.7(4) |
| Si(1)-P-Si(2)  | 105.7(2) | P-In(2)-C(211)       | 106.4(3) |
| P-In(1)-C(111) | 115.9(3) | P-In(2)-P'           | 86.4(1)  |
| P-Si(1)-C(11)  | 107.2(5) | P-In(2)-C(211')      | 113.9(3) |
| P-Si(1)-C(12)  | 112.5(5) | C(211)-In(2)-C(211') | 123.7(3) |
| P-Si(1)-C(13)  | 109.9(4) | In(1)-C(111)-Si(11)  | 123.2(6) |
| P-Si(2)-C(21)  | 111.4(5) | In(2)-C(211)-Si(21)  | 122.3(5) |

---

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)  
Chemistry Division, Code 1113  
800 North Quincy Street  
Arlington, VA 22217-5000

Commanding Officer (1)  
Naval Weapons Support Center  
Dr. Bernard E. Douda  
Crane, IN 47522-5050

Dr. James S. Murday (1)  
Chemistry Division, Code 6100  
Naval Research Laboratory  
Washington, DC 20375-5000

Dr. Richard W. Drisko (1)  
Naval Civil Engineering Lab.  
Code L52  
Port Hueneme, CA 93043

Dr. Robert Green, Director (1)  
Chemistry Division, Code 385  
Naval Weapons Center  
China Lake, CA 93555-6001

Dr. Harold H. Singerman (1)  
David Taylor Research Center  
Code 283  
Annapolis, MD 21402-5067

Dr. Eugene C. Fischer (1)  
Code 2840  
David Taylor Research Center  
Annapolis, MD 21402-5067

Chief of Naval Research (1)  
Special Assistant for Marine  
Corps Matters  
Code 00MC  
800 North Quincy Street  
Arlington, VA 22217-5000

Dr. Elek Lindner (1)  
Naval Ocean Systems Center  
Code 52  
San Diego, CA 92152-5000

Defense Technical  
Information Center (2)  
Building 5, Cameron Station  
Alexandria, VA 22314