


**AD-A243 149**

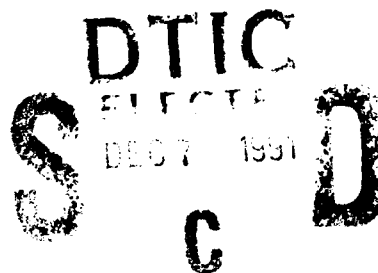

OFFICE OF NAVAL RESEARCH

Grant N00014-90-J-1193

TECHNICAL REPORT No. 70

Percolation Effects on the Decay of Admolecules

by

D. L. Lin, X. Li, Zhen-Ya Li and Thomas F. George

Prepared for publication

in

*Physical Review B*

Departments of Chemistry and Physics  
Washington State University  
Pullman, WA 99164-1046

December 1991

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

**91-17251**



UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

## REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                          |       |                                          |                                                                                                                   |                                                                           |                    |                         |
|--------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------|------------------------------------------|-------------------------------------------------------------------------------------------------------------------|---------------------------------------------------------------------------|--------------------|-------------------------|
| 1a. REPORT SECURITY CLASSIFICATION<br>Unclassified                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                       |       |                                          | 1b. RESTRICTIVE MARKINGS                                                                                          |                                                                           |                    |                         |
| 2a. SECURITY CLASSIFICATION AUTHORITY                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                    |       |                                          | 3. DISTRIBUTION/AVAILABILITY OF REPORT<br>Approved for public release; distribution unlimited                     |                                                                           |                    |                         |
| 2b. DECLASSIFICATION/DOWNGRADING SCHEDULE                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                |       |                                          |                                                                                                                   |                                                                           |                    |                         |
| 4. PERFORMING ORGANIZATION REPORT NUMBER(S)<br>WSU/DC/91/TR-70                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                           |       |                                          | 5. MONITORING ORGANIZATION REPORT NUMBER(S)                                                                       |                                                                           |                    |                         |
| 6a. NAME OF PERFORMING ORGANIZATION<br>Depts. Chemistry & Physics<br>Washington State University                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                         |       | 6b. OFFICE SYMBOL<br>(if applicable)     |                                                                                                                   | 7a. NAME OF MONITORING ORGANIZATION                                       |                    |                         |
| 6c. ADDRESS (City, State, and ZIP Code)<br>428 French Administration Building<br>Pullman, WA 99164-1046                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                  |       |                                          | 7b. ADDRESS (City, State, and ZIP Code)<br>Chemistry Program<br>800 N. Quincy Street<br>Arlington, Virginia 22217 |                                                                           |                    |                         |
| 8a. NAME OF FUNDING/SPONSORING ORGANIZATION<br>Office of Naval Research                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                  |       | 8b. OFFICE SYMBOL<br>(if applicable)     |                                                                                                                   | 9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER<br>Grant N00014-90-J-1193 |                    |                         |
| 8c. ADDRESS (City, State, and ZIP Code)<br>Chemistry Program<br>800 N. Quincy Street<br>Arlington, Virginia 22217                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                        |       |                                          | 10. SOURCE OF FUNDING NUMBERS                                                                                     |                                                                           |                    |                         |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                          |       |                                          | PROGRAM ELEMENT NO.                                                                                               | PROJECT NO.                                                               | TASK NO.           | WORK UNIT ACCESSION NO. |
| 11. TITLE (Include Security Classification)<br>Percolation Effects on the Decay of Admolecules                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                           |       |                                          |                                                                                                                   |                                                                           |                    |                         |
| 12. PERSONAL AUTHOR(S)<br>D. L. Lin, X. Li, Zhen-Ya Li and Thomas F. George                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                              |       |                                          |                                                                                                                   |                                                                           |                    |                         |
| 13a. TYPE OF REPORT                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                      |       | 13b. TIME COVERED<br>FROM _____ TO _____ |                                                                                                                   | 14. DATE OF REPORT (Year, Month, Day)<br>December 1991                    |                    | 15. PAGE COUNT<br>16    |
| 16. SUPPLEMENTARY NOTATION<br>Prepared for publication in <u>Physical Review B</u>                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                       |       |                                          |                                                                                                                   |                                                                           |                    |                         |
| 17. COSATI CODES                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                         |       |                                          | 18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)                                 |                                                                           |                    |                         |
| FIELD                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                    | GROUP | SUB-GROUP                                | ADMOLECULES PERCOLATION EFFECTS                                                                                   |                                                                           |                    |                         |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                          |       |                                          | COMPOSITE SUBSTRATE DC CONDUCTION THRESHOLD                                                                       |                                                                           |                    |                         |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                          |       |                                          | DECAY BULK THRESHOLD                                                                                              |                                                                           |                    |                         |
| 19. ABSTRACT (Continue on reverse if necessary and identify by block number)<br><br>Effects of percolation on the energy transfer from an admolecule to a two-component granular composite substrate are investigated. The substrate material is a random mixture of a metal and an insulator non-absorptive to the light. The luminescence decay rate of the admolecule near the composite surface is calculated by means of the effective medium theory as a function of the volume fraction of the metallic granules. It is found that the decay rate is greatly enhanced around the dc conduction percolation threshold at low transition frequencies. For high frequencies, the decay rate peaks at a higher volume fraction of the metallic particles, indicating the existence of a "bulk percolation" threshold. |       |                                          |                                                                                                                   |                                                                           |                    |                         |
| 20. DISTRIBUTION/AVAILABILITY OF ABSTRACT<br><input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                             |       |                                          | 21. ABSTRACT SECURITY CLASSIFICATION<br>Unclassified                                                              |                                                                           |                    |                         |
| 22a. NAME OF RESPONSIBLE INDIVIDUAL<br>Dr. David L. Nelson                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                               |       |                                          | 22b. TELEPHONE (Include Area Code)<br>(202) 696-4410                                                              |                                                                           | 22c. OFFICE SYMBOL |                         |

Percolation effects on the decay of admolecules

D. L. Lin, X. Li and Zhen-Ya Li\*  
Department of Physics and Astronomy  
State University of New York at Buffalo  
Buffalo, New York 14260

Thomas F. George  
Departments of Chemistry and Physics  
Washington State University  
Pullman, Washington 99164-1046

|                    |                                     |
|--------------------|-------------------------------------|
| Accession For      |                                     |
| NTIS GRA&I         | <input checked="" type="checkbox"/> |
| DTIC TAB           | <input type="checkbox"/>            |
| Unannounced        | <input type="checkbox"/>            |
| Justification      |                                     |
| By                 |                                     |
| Distribution/      |                                     |
| Availability Codes |                                     |
| Dist               | Avail and/or Special                |
| A-1                |                                     |

Abstract

Effects of percolation on the energy transfer from an admolecule to a two-component granular composite substrate are investigated. The substrate material is a random mixture of a metal and an insulator non-absorptive to the light. The luminescence decay rate of the admolecule near the composite surface is calculated by means of the effective medium theory as a function of the volume fraction of the metallic granules. It is found that the decay rate is greatly enhanced around the dc conduction percolation threshold at low transition frequencies. For high frequencies, the decay rate peaks at a higher volume fraction of the metallic particles, indicating the existence of a "bulk percolation" threshold.

PACS numbers: 81.40.Tv, 64.60.Ak, 78.20.-e

\* On leave of absence from Suzhou University, Suzhou 215006, China.

## I. Introduction

It is well known that in a two-component particle composite material, the conductivity exhibits singular behavior near a percolation threshold, namely, a composition at which one of the constituents forms a connected path extending throughout the material.<sup>1</sup> As an example, the effective conductivity of a composite material composed of metal and insulator particles varies as  $(q-q_c)^{-t}$ , near the metal percolation threshold  $q_c$ , where  $q$  is the volume fraction of the metal and  $t$  is a characteristic exponent which remains to be determined. Similar behavior has also been found for the nonlinear susceptibility in the static limit.<sup>2</sup>

In addition to static properties, optical properties of the two-component composite material, both linear and nonlinear, have been extensively studied.<sup>3-9</sup> In general, composite materials have optical properties very different from those of their constituents, especially in the vicinity of the percolation threshold. For instance, the observation of a large enhancement ( $10^6$ - $10^8$ ) of the effective optical nonlinearity has been reported<sup>7</sup> in composite materials. It is therefore interesting to investigate their optical properties near the percolation threshold.

On the other hand, optical properties of an atomic system located near a solid surface can change qualitatively depending upon the structure of the substrate. Detailed information about the spectroscopic properties of the adspecies can be employed to probe the electronic and optical properties of the substrate. A recent study of the decay rate and resonance fluorescence spectrum of a molecule adsorbed near the surface of a particle composite<sup>10</sup> illustrates clearly the strong dependence of the energy transfer on the volume fraction of the impurity.

We investigate in this communication the effect of percolation on the energy transfer between an admolecule and the substrate. We consider a two-component granular material, that is, a random mixture of two kinds of small particles: one is an insulator not absorptive to the light, and the other is a metal. Optical properties of this material are described by an effective dielectric function derived by means of the effective medium theory (EMT).<sup>1,11-13</sup> When one component of the composite just forms an infinite connected path through the material, it is at the percolation threshold. Thus, the conductivity increases suddenly when the metal granules just reach the percolation threshold. Our purpose is to investigate the luminescence decay rate of an admolecule near the surface of the composite which is in the vicinity of its percolation threshold. It is found that the decay rate shows a peak centered around the conduction percolation threshold at low frequencies, or when  $\omega \ll \omega_p$ , where  $\omega_p$  is the plasmon frequency of the metal. For admolecules of high transition frequency, or  $\omega \sim \omega_p$ , the peak occurs at a higher  $q$ , indicating the possible existence of another percolation threshold. Implications of this and other results will be discussed.

## II. Theory

We consider a molecule adsorbed at a distance  $d$  from the surface of a two-component particle composite material as the substrate. For simplicity, we assume that the molecule has only two levels  $|+$  and  $|-\rangle$  with an energy difference  $E_+ - E_- = \hbar\omega$ .

The optical spectrum of the scattered field from an admolecule can in general be treated by means of a set of surface-dressed optical Bloch equations<sup>14</sup> including effects of the surface-reflected field. For the present purpose of the luminescence decay-rate study, it is sufficient to consider the

admolecule as a damped harmonic oscillator. Thus, the Hamiltonian of the system is given by

$$H = (\omega - i\gamma_0) a^\dagger a - p^* a^\dagger E_R, \quad (1)$$

where  $a^\dagger(a)$  is the creation (annihilation) operator for the molecular dipole oscillator whose matrix element is denoted by  $p$ , and  $E_R$  denotes the reflected electric field in the direction of the dipole moment. Following Dekker's quantization procedure for dissipative systems,<sup>15</sup> the equation of motion for the density operator of the molecular system can be written as

$$\dot{\rho} = -\frac{i}{\hbar} [a^\dagger, [a, H]\rho] + \frac{i}{\hbar} [\rho [H^\dagger, a^\dagger], a] \quad (2)$$

With the help of Eqs. (1) and (2), we find that the mean value of the operator obeys the equation

$$\frac{d}{dt} \langle a \rangle = \text{Tr} \langle \dot{\rho} a \rangle = -i(\omega + \Delta\omega) \langle a \rangle - \gamma \langle a \rangle, \quad (3)$$

with the decay rate given by

$$\gamma = \gamma_0 \left[ 1 + \frac{3}{2\sqrt{\epsilon_1} \kappa_0^3} \text{Im}(E_R/\mu_0) \right] \quad (4)$$

In the above derivation, we have made use of the following definitions. Both the frequency shift  $\Delta\omega$  and width change  $\Delta\gamma = \gamma - \gamma_0$  are caused by the presence of the surface. The decay rate of the excited molecule inside a homogeneous medium is  $\gamma_0 = \frac{2}{3} \sqrt{\epsilon_1} |p|^2 \omega^3 / c^3$ , and the dipole moment operator is  $\mu_0 = pa$ . In

addition, we have assumed that the molecule is in a medium of dielectric constant  $\epsilon_1$ , and  $\kappa_0 = \omega/c$ .

As is well known,<sup>10,14</sup> the reflected field  $E_R$  for an emitting dipole with moment  $\mu_0$  located near the surface of a solid substrate can be found by solving Maxwell equations with corresponding boundary conditions. Since the substrate we are considering now is a two-component particle composite material with symmetric microgeometry,  $E_R$  must depend on the optical properties of both components as well as their volume fractions. Therefore measurements of the decay rate alone can reveal much of the characteristic properties of the substrate via  $E_R$ . Here we just consider the case in which the admolecule is oriented such that its dipole moment is normal to the substrate surface. The decay rate can then be worked out from Eq. (4) by the standard procedure,<sup>10</sup> namely,

$$\gamma = 1 - \frac{3}{2} \operatorname{Re} \int_0^\infty \frac{\kappa^3 dk}{\mu_1} \frac{\epsilon_1 \mu_2 - \epsilon_2 \mu_1}{\epsilon_1 \mu_2 + \epsilon_2 \mu_1} \exp(2i\mu_1 x) , \quad (5)$$

where  $\epsilon_2$  is the effective dielectric function of the substrate,  $\mu_1 = \sqrt{1 - \kappa^2}$ ,  $\mu_2 = \sqrt{\epsilon_2 / \epsilon_1 - \kappa^2}$  and  $x = \sqrt{\epsilon_1} \omega d / c$ . The rate in Eq. (5) is measured in the unit of  $\gamma_0$ .

For a symmetric conductor-insulator particle composite, the conductivity or optical susceptibility is usually treated by the extended EMT.<sup>16</sup> The effective dielectric function  $\epsilon_2(\omega)$  is given in this theory by

$$\frac{\epsilon_2 - \epsilon_b}{\epsilon_b + (\frac{1}{q_c} - 1)\epsilon_2} q + (1-q) \frac{\epsilon_2 - \epsilon_a}{\epsilon_a + (\frac{1}{q_c} - 1)\epsilon_2} = 0 , \quad (6)$$

where  $\epsilon_a(\epsilon_b)$  stands for the dielectric function of the insulator (metal),  $q$  is the volume fraction of the conductor in the composite, and  $q_c$  is the critical volume fraction of percolation for the connection of metal particles.<sup>1</sup> In the standard EMT,  $q_c = 1/3$ .

Equation (6) can be rewritten as

$$\left(\frac{1}{q_c} - 1\right)\epsilon_2^2 - \frac{1}{q_c}[(1-q-q_c)\epsilon_a + (q-q_c)\epsilon_b]\epsilon_2 - \epsilon_a\epsilon_b = 0 \quad (7)$$

The quadratic equation (7) has in general two solutions that are complex conjugate to each other. We are interested in a physical solution  $\epsilon_2(\omega)$  which is a continuous function of  $\omega$  and has a positive imaginary part. Since the percolation threshold of a metal-insulator composite material changes with the microgeometry structure of particles,  $q_c$  may be regarded as a parameter characterizing the microstructure of the two components.

### III. Results and discussion

In our numerical analysis, we assume for definiteness a nonabsorbing insulator such as  $Al_2O_3$  with real dielectric constant  $\epsilon_a = 3$ , while the dielectric function  $\epsilon_b$  of the metal is given by

$$\epsilon_b = 1 - \frac{\omega_p^2}{\omega(\omega + i\Gamma_p)} \quad (8)$$

where  $\Gamma_p$  denotes the damping rate of the plasmon oscillation. For a typical metal such as silver, we take  $\Gamma_p = 0.01 \omega_p$ . Other parameters we have to specify are the dielectric constant  $\epsilon_1 = 1.5$  for fatty acid and  $x = 0.2$ , a

typical value which can always be satisfied by adjusting the molecular distance from the surface for a given transition frequency  $\omega$ .

We first solve Eq. (7) for the effective dielectric function  $\epsilon_2$  of the composite substrate with given  $q_c$  and  $\omega$ . Plotted as functions of the volume fraction  $q$ , both the real and imaginary parts of  $\epsilon_2$  are shown in Fig. 1 for  $q_c = 0.3$  and three typical frequencies: (a)  $\omega = 0.1 \omega_p$  in the low-frequency region: The absorption part peaks around  $q = q_c$ , where the dispersion part changes its sign. Hence the substrate is metal-like for  $q > q_c$  in low-frequency regime. Our numerical study shows similar results for different values of  $q_c$ ; (b)  $\omega = 0.35 \omega_p$ : Both the peak of the imaginary part and the zero of the real part move toward larger  $q$ ; and (c)  $\omega = \omega_p$ : The real part remains positive in the whole range, and the imaginary part has a small peak around  $q = 0.7$ . We believe that this is due to the bulk effect on the percolation threshold, which we shall discuss later.

Since the surface plasmon contribution leads to a minimum in the denominator in Eq. (7),<sup>17</sup> this resonance condition determines the dispersion relation of the surface plasmon. If the substrate is nonabsorptive, the surface plasmons have infinite lifetime and  $\epsilon_1 \mu_2 + \epsilon_2 \mu_1 = 0$ . Because of the nonzero  $\Gamma_p$  in the present case, the lifetime remains finite. In the low-frequency region, say,  $\omega/\omega_p \leq 0.2$ , the absorption part of the optical susceptibility of the composite material is usually very large, as seen in Fig. 1(a), and hence the damping rate is too large for surface plasmons to propagate. In the high-frequency region,  $\omega/\omega_p \geq 0.9$ , it is seen from Fig. 1(c) that the real part of  $\epsilon_2$  is always positive even though the imaginary part is much smaller. There can not be surface plasmon waves here either, because the real part of  $\epsilon_2$  must be negative (at least) for surface modes to exist.<sup>18</sup>

The decay rate is computed from (5) with  $\epsilon_2(\omega)$  given by (7). Since we are interested in percolation effects on the energy transfer from the admolecule to the surface,  $\gamma$  is calculated as a function of the volume fraction  $q$  of the metal particles and is expressed in the unit of  $\gamma_0$ . It is well known that the conduction percolation threshold  $q_c$  depends sensitively upon the microstructure of the two-component system. For a metal-insulator system of symmetric microgeometry,  $q_c$  is not expected to exceed 0.5 normally. Some of our results are shown in Fig. 2, in which we have chosen the frequency ratio  $\omega/\omega_p$  such that there are almost no surface plasmons propagating on the substrate surface. Curves 1 and 2 in both cases (a) and (b) correspond to low frequencies ( $\omega = 0.1 \omega_p$ ) and high frequencies ( $\omega = \omega_p$ ), respectively. Since surface plasmon waves are absent in these cases, the enhancement of the decay rate in every case shown in the figures must be due to absorption by metallic granules. We attempt below to understand qualitatively the peaks in these curves.

In the low-frequency regime, the absorption peak appears at around the conduction percolation threshold  $q_c$  of metallic granules, qualitatively in agreement with what has been found in Ref. 3 in which a simple model of  $q_c = 1/3$  is assumed. This is understandable because only at  $q \sim q_c$  there is sufficient metal component to absorb the energy transferred from the excited admolecule. As  $q$  increases further, metallic particles become closer to a bulk metal and the absorption rate is reduced again. This is because the collisions of carriers responsible for the absorption are usually more frequent in metallic particles than in the bulk. In the high-frequency regime, the position of the absorption peak can be very different for different  $q_c$ . When  $q_c = 0.3$ , curve 2 peaks at about  $q = 0.7$  in Fig. 1(a), and when  $q_c = 0.5$ , it peaks at  $q_c$  in Fig. 1(b). To account for this interesting

phenomenon, we believe that in the optical wavelength range there exist two distinct percolation thresholds, where one results from the usual percolation formed by one connected path extending throughout the material and the other from the "surface percolation" formed by so many connected paths that almost the whole cross section is conducting.<sup>19</sup> For low frequencies, the usual percolation dominates and the optical behavior of the composite material is similar to that of the static case.<sup>2,20</sup> For high frequencies, the bulk of the metallic part in the granular material is responsible for the optical absorption in the substrate. Hence the peak of curve 2 clearly indicates the existence of a new percolation threshold resulting from the bulk effects.

When the transition frequency is such that there exist surface plasmon waves in the substrate, energy can be transferred from the excited admolecule both by the absorption processes described above and the excitation of surface plasmon waves. The latter is found much more important than the former. Numerical results are plotted in Fig. 3 for some typical cases. It is clearly seen that the decay rate is greatly enhanced, especially when  $q \sim 0.75$  for  $q_c = 0.3$  and when  $q \sim 0.85$  for  $q_c = 0.5$ . A physical understanding of this behavior, however, is not straightforward, and further investigation is required.

This research was supported in part by the Office of Naval Research and the National Science Foundation under Grant CHE-9016789.

## References

1. G. Deutscher, R. Zallen and J. Adler ets., *Percolation Structures and Processes*, (Israel Physical Society, Jerusalem, 1983); S. Kirkpatrick, *Rev. Mod. Phys.* 45 474 (1973).
2. D. Stroud and P. M. Hui, *Phys. Rev. B* 37, 8719 (1988).
3. D. Stroud, *Phys. Rev. B* 19, 1783 (1979).
4. D. Stroud and Van E. Wood, *J. Opt. Soc. Am. B* 6 778 (1989).
5. P. Sheng, *Physica A* 157 238 (1989).
6. D. Ricard, *Physica A* 157, 301 (1989).
7. D. Ricard, P. Roussignol and C. Flytzanis, *Opt. Lett.* 10 511 (1985); F. Hache, D. Ricard and C. Flytzanis, *J. Opt. Soc. Am. B* 3 1647 (1986); D. Ricard, F. Hache, P. Roussignol and C. Flytzanis, Optical nonlinearities of composite materials," in *Digest of Topical Meeting on Nonlinear Optical Properties of Materials* (Optical Society of America, Washington, D.C., 1988), pp. 202-205.
8. Y. Wang and W. Mahler, *Opt. Commun.* 61, 233 (1987); Y. Wang, W. Mahler, N. Herron and A. Suna, "Linear and nonlinear optical properties of semiconductor clusters," in *Digest of Topical Meeting on Nonlinear Optical Properties of Materials* (Optical Society of America, Washington, D.C., 1988), pp. 206-208.
9. A. E. Neeves and M. H. Birnboim, *J. Opt. Soc. Am. B* 6, 787 (1989); J. W. Haus, N. Kalyaniwalla, R. Inguva, M. Bloemer and C. M. Bowden, *J. Opt. Soc. Am.* 6, 797 (1989).
10. X. S. Li, D. L. Lin, T. F. George, Y. Liu and Q. Gou, *Phys. Lett. A* 145, 444 (1990).
11. D. A. G. Bruggenman, *Ann. Phys. (Leipzig)* 24 636 (1935).

12. P. Sheng in *Homogenization and Effective Moduli of Materials and Media*, ed. by J. L. Ericksen, D. Kinerlehier, R. Kohn and U.-L. Lions (Springer-Verlag, New York, 1986) p. 196 ff.
13. R. Landauer, *J. Appl. Phys.* 23, 779 (1952); M. Nakamura, *Phys. Rev. B* 28, 2216 (1983).
14. X. Y. Huang, J. T. Lin and T. F. George, *J. Chem. Phys.* 80, 893 (1984); X. S. Li, D. L. Lin and T. F. George, *Phys. Rev. B* 4,
15. H. Dekker, *Physica A* 95, 311 (1979).
16. M. Nakamura, *Phys. Rev. B* 29, 3691 (1984).
17. G. S. Agarwal, *Phys. Rev. A* 11, 230, 243, 253 (1975); 12, 1475 (1975).
18. V. M. Agranovich and D. L. Mills, Eds., *Surface Polaritons* (North-Holland, Amsterdam, 1982).
19. H. E. Roman, A. Bunde and W. Dieterich, *Phys. Rev. B* 34, 3439 (1986).
20. F. Brouers, *J. Phys. C* 19, 7183 (1986).

# Figure Captions

1. Effective dielectric function  $\epsilon_2(\omega)$  vs volume fraction of metallic particles for  $q_c = 0.3$ . The solid (dashed) lines represent the real (imaginary) part of  $\epsilon_2(\omega)$ . (a)  $\omega/\omega_p = 0.1$ , (b)  $\omega/\omega_p = 0.35$  and (c)  $\omega/\omega_p = 1.0$
2. Luminescence decay rate  $\gamma$  of the admolecule as a function of  $q$ . Curve 1 is for  $\omega/\omega_p = 0.1$  and curve 2 is for  $\omega/\omega_p = 1.0$ . (a)  $q = 0.3$  and (b)  $q = 0.5$ .
3. Luminescence decay rate  $\gamma$  of the admolecule vs.  $q$  in the frequency region where the energy transfer from the admolecule to surface plasmons occurs. Curve 1:  $q_c = 0.3$ ,  $\omega/\omega_p = 0.35$ ; Curve 2:  $q_c = 0.5$ ,  $\omega/\omega_p = 0.45$ .

Fig. 1

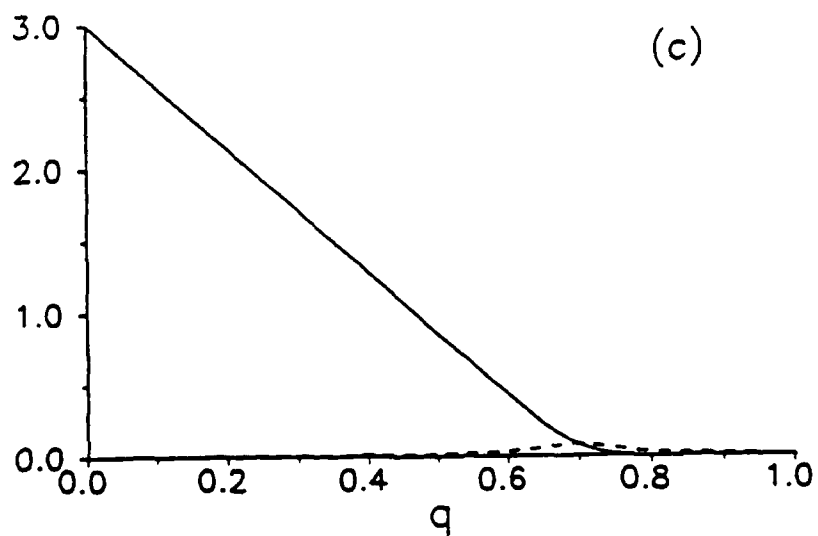
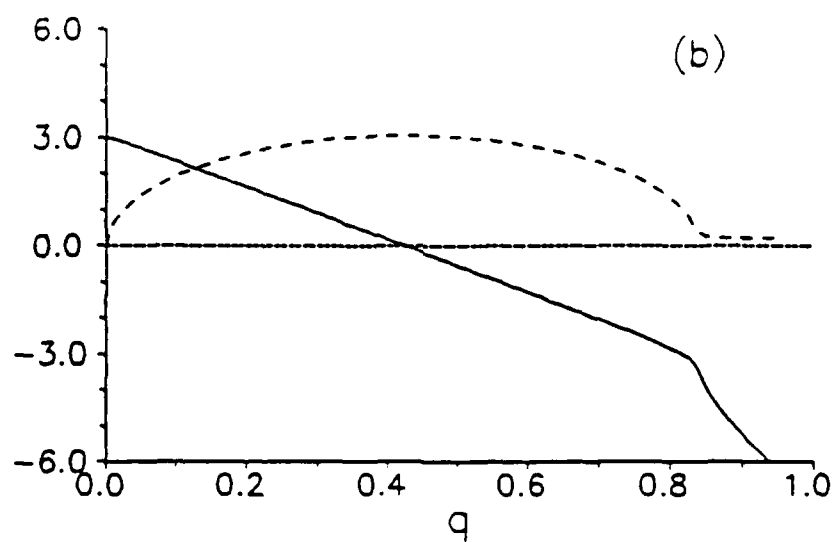
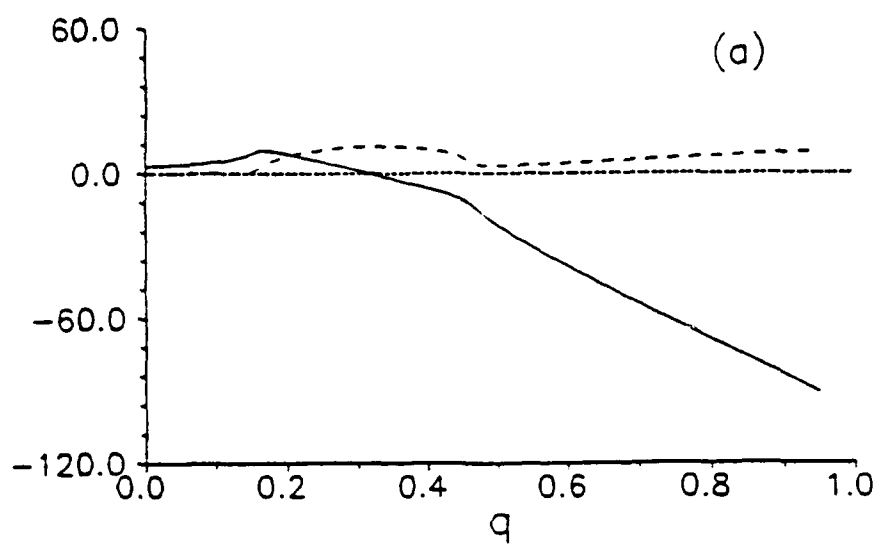


Fig. 2


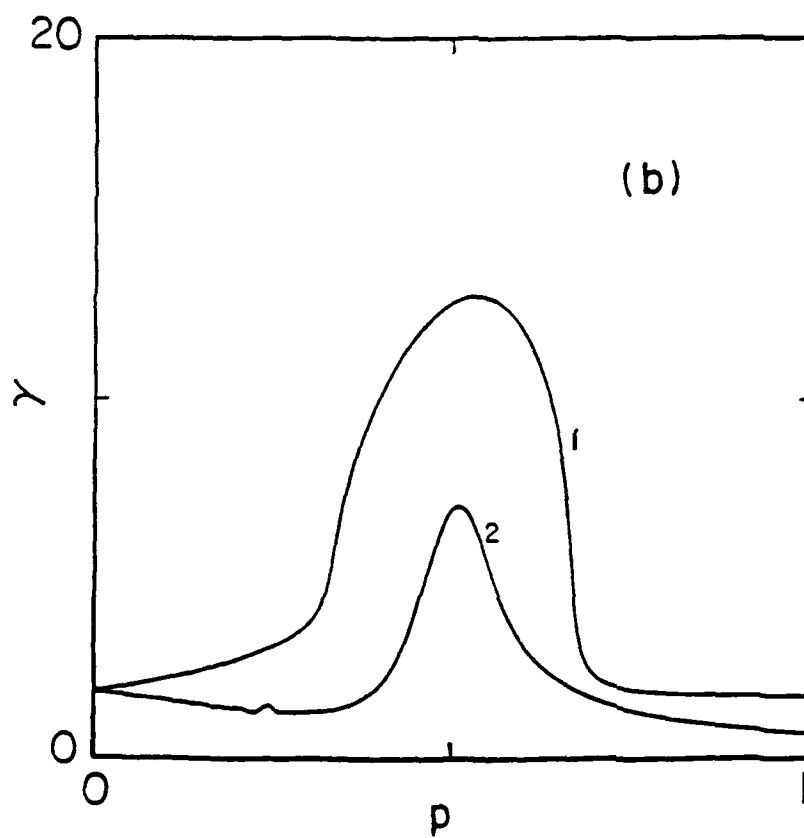


Fig. 3

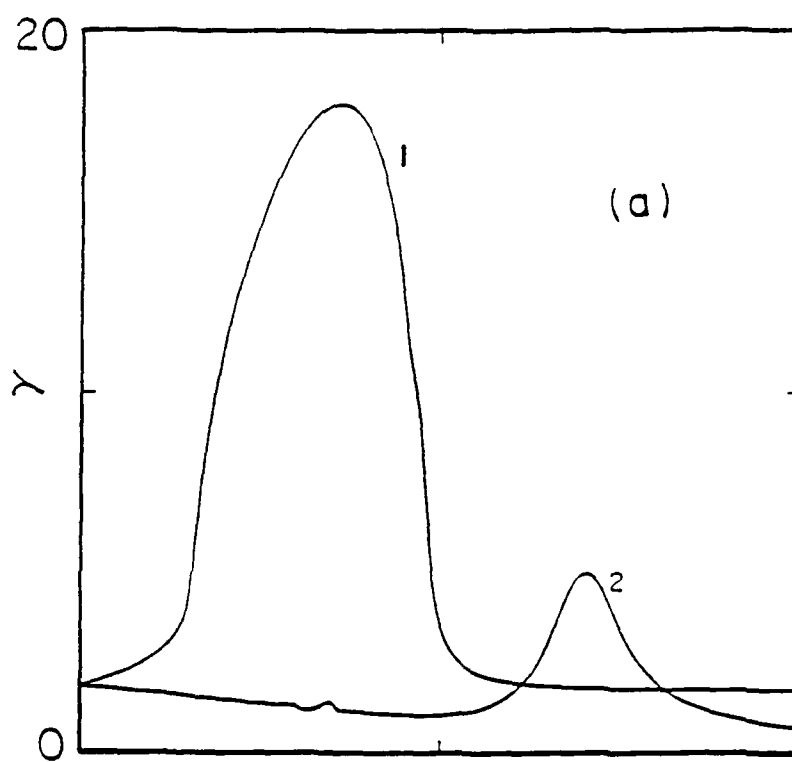