


AD-A243 151



✓ ②

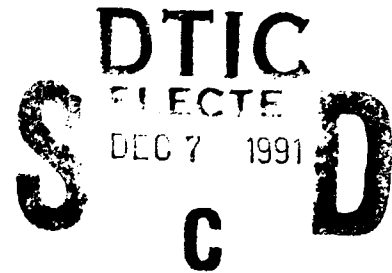

OFFICE OF NAVAL RESEARCH

Contract: N00014-85-K-0222

Work Unit: 4327-555

Scientific Officer: Dr. Richard S. Miller

Technical Report No. 29

A TRIANGULAR DOUBLE CANTILEVER BEAM TEST FOR MEASURING ADHESIVE OR
COHESIVE FRACTURE ENERGY

by

G. Liu and A. N. Gent

Institute of Polymer Engineering

The University of Akron

Akron, Ohio, 44325-0301

December 1991

Reproduction in whole or in part is permitted for any purpose
of the United States Government

Approved for public release; distribution unrestricted

91-17317



4/28/81

91 1200 023

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 29	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) <u>A Triangular Double Cantilever Beam Test For Measuring Adhesive Or Cohesive Fracture Energy</u>		5. TYPE OF REPORT & PERIOD COVERED Technical Report
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) G. Liu and A. N. Gent		8. CONTRACT OR GRANT NUMBER(s) N00014-85-K-0222
9. PERFORMING ORGANIZATION NAME AND ADDRESS Institute of Polymer Engineering The University of Akron Akron, OH 44325-0301.		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 4327-555
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Power Program Arlington, VA 22217-5000		12. REPORT DATE December 1991
		13. NUMBER OF PAGES 28
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) According to attached distribution list. Approved for public release; distribution unrestricted.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Submitted to: Journal of Adhesion		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Adhesion, Adhesion Test, Cantilever Beam, Cohesive Fracture, Crack Growth, Fracture, Strength Measurement, Strength Test		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) A thin layer of adhesive bonded between two stiff elastic plates of uniform thickness and triangular in shape is recommended as a test specimen for measuring cohesive or adhesive strength. A similar test was employed many years ago by Mostovoy <u>et al</u> (1,2) but appears to have received little attention in the intervening period. Nevertheless, it has marked advantages in comparison with current ASTM tests in simplicity of construction and use. Examples are given using silicone rubber layers bonded between steel plates.		

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

S/N 0102-LF-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)



Accession For	
NTIS	ORAI ☒
DTIC	Tab ☐
Unannounced	☐
Classification	

A Triangular Double Cantilever Beam Test For Measuring

Adhesive Or Cohesive Fracture Energy

G. Liu and A. N. Gent
Department of Polymer Engineering
University of Akron, Akron, OH 44325-0301

Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

Abstract

A thin layer of adhesive bonded between two stiff elastic plates of uniform thickness and triangular in shape is recommended as a test specimen for measuring cohesive or adhesive strength. A similar test was employed many years ago by Mostovoy et al (1,2) but appears to have received little attention in the intervening period. Nevertheless, it has marked advantages in comparison with current ASTM tests in simplicity of construction and use. Examples are given using silicone rubber layers bonded between steel plates.

1. Introduction.

Double Cantilever Beam (DCB) tests have been widely used to measure the strength of stiff structural adhesives (1-5) because the experiments are simple to perform and analyse. The specimens consist of two simple rectangular plates, with a layer of adhesive sandwiched between them. Linear elastic fracture mechanics may be used to compute the fracture energy, i.e., the critical rate G_c of release of strain energy stored in the bent beams as the crack advances, from the applied force required to propagate the crack and some geometrical terms. However, in its simplest form the test has a serious shortcoming: the energy G_c available for

fracture decreases continuously as the crack length increases. It is therefore necessary to measure the crack length c at any instant, as well as the applied cleavage force P or separation u of the beam ends, in order to determine the fracture energy G_i . (The critical value is denoted G_a or G_c , for adhesive or cohesive failure, respectively.)

Because of this difficulty, contoured beams have been adopted rather widely, with a cross-section chosen to give a constant relation between applied force and G_i , independent of crack length. Either the thickness or the width of the beams can be varied, but it seems more usual to vary the thickness approximately in proportion to $c^{2/3}$ (when the crack length is much greater than the beam thickness) as discussed in the following section, to give a constant geometrical factor relating the applied force P to G_i (2,4,5). However, such beams seem to be rather difficult to make in comparison to beams with constant thickness and varying width. We have therefore examined the feasibility of using triangular-shaped beams of uniform thickness, as shown in Figure 1, which also give a constant geometrical factor.

The width-tapered DCB test (Figure 2) was first proposed by Mostovoy et al (1,2). Although they obviously recognized its advantages, they actually used somewhat more complicated shapes, in part to avoid possible errors arising from the assumption of a "built-in" end condition for the two beams at the crack front, and in part to allow for the application of the cleavage force at a

point other than the beam tips. An example is given in Figure 2. We have used a simpler geometry, a pair of triangular steel plates, Figure 1. Metal wires brazed around the tips of the triangular plates allowed the force to be applied almost exactly at this point, without seriously affecting the elastic response of the beams. In this case a very simple expression for the fracture energy is obtained:

$$G_c = 12P^2/EK^2D^3 \quad (1)$$

where P is the applied force to propagate the crack, E is Young's modulus of the steel plates, $K = 2\tan(\theta/2)$ where θ is the wedge angle of the plates, and D is the plate thickness. Note that the fracture force P is independent of crack length.

Measurements have been made of cohesive and adhesive strengths of test specimens prepared by bonding a flexible silicone resin between triangular steel plates. The results are compared with theoretical predictions for this geometry and with independent measurements of strength.

2. Theoretical considerations.

For linearly-elastic systems the relation between fracture energy G_c and applied force P is given by (6):

$$G_c = \frac{1}{2} P^2 (\partial C / \partial A) \quad (2)$$

For double cantilever beam specimens, with beams of constant width B , and thickness D varying with distance c from the point of application of force in the form:

$$D = K_1 c^{2/3} \quad (3)$$

where K_1 is a constant, the compliance is given by

$$C = 24c/EBK_1^3 \quad (4)$$

and the crack area $A = Bc$. Thus, the fracture energy is obtained from Equation 2 as

$$G_I = 12P^2/EB^2K_1^3 \quad (5)$$

and the fracture force P is independent of crack length c .

Similarly, for the triangular double cantilever test shown in Figure 1, the width B is proportional to the crack length c , i.e., $B = Kc$ where $K = 2\tan(\theta/2)$, and the crack area $A = Kc^2/2$ (provided that the angle θ is not too large). The compliance C , given by the ratio of the separation u of the beam tips to the cleavage force P , is then obtained as:

$$C = u/P = 12C^2/EKD^3, \quad (6)$$

and the fracture energy is obtained from Equation 2 as

$$G_I = 12P^2/EK^2D^3. \quad (7)$$

Note that the fracture force is again independent of the crack length when the fracture energy is constant.

3. Experimental.

3.1 Preparation of steel surfaces.

Three pairs of 4140 steel plates ($\theta=15^\circ$, 20° , and 30.7°) with a length of 280 mm and thickness of 3.17mm were roughened with sandpaper (3M Company, medium grade), washed with acetone, and dried in air. The cleaned steel plates were immersed in a solution of Primer 92023 (Dow Corning) for 1 hour and dried in air overnight to allow the solvent to evaporate. They were then heated to 80°C for 2 hours to promote the reaction between primer and steel.

3.2 Preparation of silicone rubber sheets.

Sylgard 184 curing agent was mixed with Sylgard 184 silicone resin (both from Dow Corning) at a concentration of 8 parts by ^{weight}~~volume~~ per 100 parts of resin. The mixture was degassed

for 30 minutes in a vacuum chamber, and then cast as a 1mm thick sheet at room temperature for 12 hours. During this time the silicone rubber became partly cured, but it was still sticky and adhered well to other surfaces.

3.3 Preparation of test specimens.

A thin coating of 3145 RTV adhesive (Dow Corning) was applied to two primed triangular steel plates. A previously-prepared silicone rubber sheet was then placed between the two plates, as shown in Figure 3. The assembly was held together by "C" clamps for two hours at room temperature followed by 12 hours at 60°C, and then cooled down slowly to room temperature.

3.4 Test method.

Wires of 2mm diameter were welded to the tips of the steel plates as shown in Figure 3 so that a cleavage force could be applied directly to them. Light steel chains were used to connect the wire loops to the upper and lower clamps of an Instron tensile test machine. The wide end of the specimen was supported lightly to maintain the specimen horizontal. Forces were then applied to pull the tips of the two steel plates apart at a speed of 0.5mm/min. During the experiment the position of the support was adjusted to keep the plane of the specimen at right angles to the applied force.

4. Results and discussion.

4.1 Cohesive fracture energy.

Cohesive fracture took place approximately in the mid-plane of a well-bonded silicone rubber sheet. However, many subsidiary cracks were observed, running generally perpendicular to the main fracture plane and penetrating almost to the bonded surfaces. A representative view of part of the fracture plane is shown in Figure 4. These subsidiary cracks are tentatively attributed to fracture of silicone rubber under the high dilatant stresses set up as the stiff steel plates are forced apart, a form of cavitation (7). Soft incompressible solids cannot withstand dilatant stresses greater than about the value of their Young's modulus (about 2 MPa for these silicone rubber formulations) without suffering internal cracking (8). It is noteworthy that, although the cracks ran for long distances, up to about 80 mm, following rather irregular paths, they lay generally about 10 mm apart, a distance close enough to reduce significantly the dilatant stress set up in the material lying between them.

A constant fracture force was obtained after the main fracture began to propagate, Figure 5. The force was also found to be directly proportional to the value of K ($= 2\tan(\theta/2)$), Figure 6. This is in accord with Equation 7. Values of cohesive fracture energy G_c calculated by Equation 7 for specimens with different angles are listed in Table 1. The crack propagation rate was measured to be 2.8 mm/min. A consistent value of cohesive fracture energy was obtained, Table 1, of about 210 J/m², which

agrees very well with that obtained independently, $214 \pm 15 \text{ J/m}^2$, by tearing a pre-scored silicone rubber sheet in a trouser test at a rate of tear propagation of 2.5 mm/min.

4.2 Adhesive fracture energy.

The triangular DCB test is also suitable for measuring adhesive fracture energy. When 3145 RTV adhesive was applied to only one of the primed plates, fairly good adhesion was obtained on one surface, between 3145 RTV adhesive and silicone rubber, but not on the other, between silicone rubber and steel. Adhesive fracture took place between the silicone rubber and steel surface, at a fracture force P of $75 \pm 3 \text{ N}$ at a rate of crack propagation of 7 mm/min. From Equation 7, using the relevant values of $\theta = 30.7^\circ$ and $D = 3.17 \text{ mm}$, the fracture energy G_c is obtained as only $36 \pm 3 \text{ J/m}^2$.

4.3 Plate dimensions.

It is important that no plastic yielding occurs in the stiff plates under the test conditions. A minimum thickness for the plates can be estimated from simple bending theory. If a triangular plate, with length c , is bent by a constant force P , Figure 1, the maximum tension or compression stress is $\sigma_{\max} = ED/2R$, where R is the radius of curvature, given by $EI/M(c)$, and $M(c) = Pc$. Thus, the maximum stress is:

$$\sigma_{\max} = PCD/2I \quad (8)$$

where $I = KcD^3/12$. Thus, from equations 7 and 8:

$$\sigma_{\max} = (3G_c E/D)^{1/2} \quad (9)$$

In our experiments the yield strength of 4140 steel is 665MPa (9) and E is 200 GPa. G_c for silicone rubber is about 200 J/m². Thus the steel plates must have a thickness greater than about 0.5 mm to avoid yielding.

4.4 An alternative configuration.

An alternative geometry for the tapered DCB test uses trapezoidal plates with an end width B_0 , Figure 7. The cleavage force P is applied at this end of the specimen. As shown in the Appendix, the fracture energy G_c is given by

$$G_c = (12P^2/EK^2D^3) [1+(9\alpha/4)] / (1+\alpha) [1+(3\alpha/2)]^2 \quad (10)$$

where $\alpha = B_0/Kc$. Compared with equation 7, the factor α is introduced, leading to a dependence of the fracture force P on crack length. This dependence is small if the tip width B_0 is small compared to the width Kc of plate at the crack front.

The cohesive fracture energy G_c of a similar silicone rubber (10 parts of Sylgard 184 curing agent per 100 parts of silicone resin, cured at 80°C for 6 hours) was measured in a trapezoidal DCB

test at a crack speed of 0.8 mm/min. The result was 120 ± 15 J/m², Table 2, which agrees very well with that from a trouser tearing test measured at a similar rate of tear propagation, 135 ± 5 J/m².

5. Conclusions.

1. Triangular DCB test specimens were employed to measure the cohesive fracture energy G_c of Sylgard 184 silicone rubber. Excellent agreement was found between values of fracture energy, G_c , about 210 J/m², for different beam angles and in different experiments.

2. The triangular DCB test was also employed to measure adhesive fracture energy G_a between silicone rubber and a steel surface. The value was much smaller, only about 36 J/m².

3. Minimum thicknesses of plates to avoid plastic yielding can be calculated by means of Equation 9.

4. A slightly modified triangular DCB test, using trapezoidal plates, was also employed and gave results in good agreement with those from a trouser tear test for the cohesive fracture energy of a more highly cured silicone rubber. However, calculation is more complicated than with triangular plates because the fracture energy depends on crack length, to a greater degree the greater the initial width B_0 relative to the crack length c .

References

1. S. Mostovoy and E. J. Ripling, Final Report N00019-75-C-0271 (1975), Naval Air Systems Command, Washington, D.C.
2. T. R. Brussat, S. T. Chiu, and S. Mostovoy, Report AFML-TR-77-163, Air Force Materials Laboratory, Wright Patterson Air Force Base, Dayton, Ohio.
3. A. J. Kinloch, "Adhesion and Adhesives: Science and Technology.", Chap. 7, Chapman and Hall, New York, 1987 .
4. "Fast Fracture and Crack Arrest.", STP 627, ed. by G. T. Hahn and M. F. Kanninen, American Society for Testing and Materials, Philadelphia, PA, 1977.
5. ASTM D3433-75, American Society for Testing and Materials, Philadelphia, PA, 1985.
6. J. G. Williams, "Fracture Mechanics of Polymers", Ellis-Horwood Limited, Chichester, England, 1984.
7. A. N. Gent and P. B. Lindley, Proc. Roy. Soc. (Lond.) A249, 195 (1958).
8. A. N. Gent and B. Park, J. Mater. Sci. 19, 1947 (1984).
9. M. M. Farag, "Materials and Process Selection in Engineering.", Applied Science Publishers, London, 1979, p.12.

Appendix

Trapezoidal beams are subjected to a force P , Figure 7. The compliance is calculated for a combination of a parallel-sided strip and a triangular plate with angle θ , as shown in Figure 7. Compliance for a parallel-sided strip (shown as 1 in Figure 7), is:

$$C_1 = 8c^3/EB_0D^3 \quad (11)$$

and compliance for a triangular plate (shown as 2 in Figure 7, width $B = Kc$), loaded at the tip, is:

$$C_2 = 12c^3/EKD^3 \quad (12)$$

Therefore, the compliance C for both pieces, is given by

$$C = 1/(C_1^{-1} + C_2^{-1}) = 12c^3 / \left(\frac{3}{2}B_0 + Kc \right) ED^3 \quad (13)$$

The crack area A is $B_0c + (Kc^2/2)$, where $K = 2\tan(\theta/2)$. The fracture energy is then obtained as

$$G_I = (12P^2/EK^2D^3) [1 + (9\alpha/4)] / (1 + \alpha) [1 + (3\alpha/2)]^2 \quad (14)$$

where $\alpha = B_0/Kc$.

Table 1. Cohesive fracture energy G_c of 8 phr Sylgard 184 silicone rubber from triangular DCB test.

θ ($^\circ$)	K	P (N)	G_c (J/m ²)
15.0	0.263	87 ± 4	206 ± 16
20.0	0.353	118 ± 8	210 ± 21
30.7	0.549	183 ± 8	209 ± 15

Table 2. Cohesive fracture energy G_c of 10 phr Sylgard 184
silicone rubber from trapezoidal DCB test: $B_0 = 9$ mm,
 $D = 1.44$ mm, $\theta = 10^\circ$ ($K = 0.175$).

P (N)	c (mm)	$B_0 + Kc$ (mm)	α	G_c (J/m ²)
16.7 ± 0.9	168	37.5	0.316	135 ± 15
15.7 ± 0.8	176	39.3	0.297	120 ± 15
14.2 ± 0.9	201	43.5	0.261	100 ± 20

Figure Legends

Figure 1. A triangular double cantilever beam specimen.

Figure 2. A tapered double cantilever beam specimen.

Figure 3. Components of a test specimen.

Figure 4. Fracture surface of silicone rubber layer, 1 mm thick.
The end width of the steel plate is 100 mm.

Figure 5. Force-displacement relation for a triangular DCB test.

Figure 6. Fracture force plotted against plate parameter K .
($K = 2\tan(\theta/2)$).

Figure 7. A trapezoidal double cantilever beam specimen.

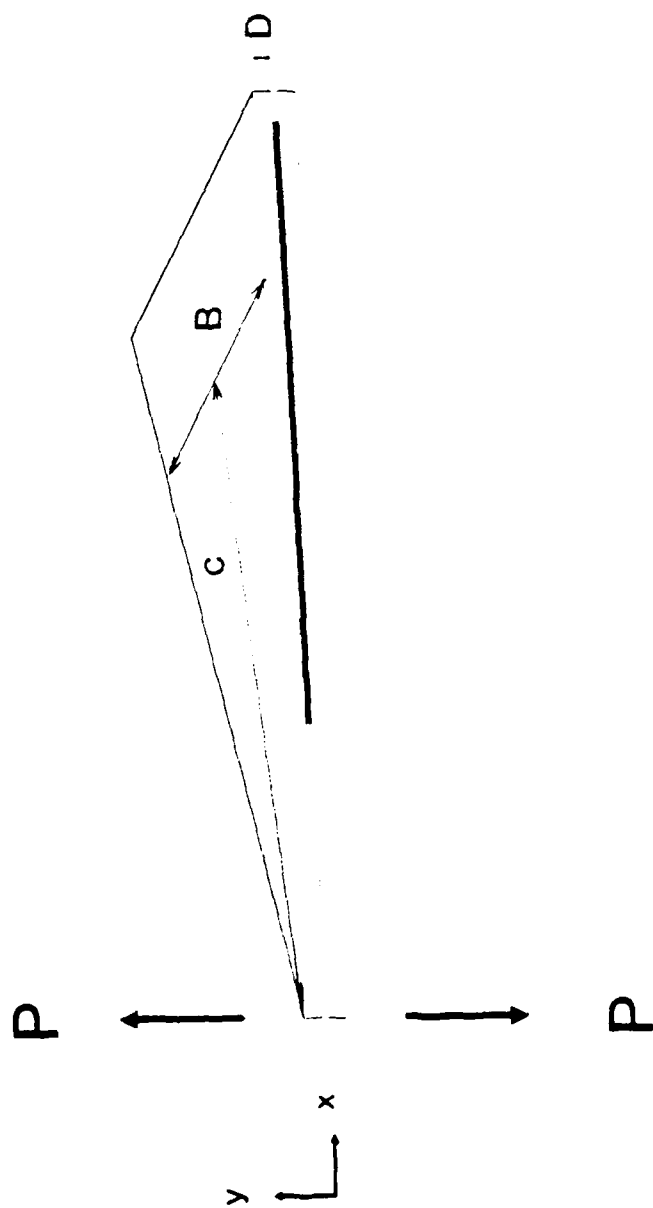


FIGURE 1

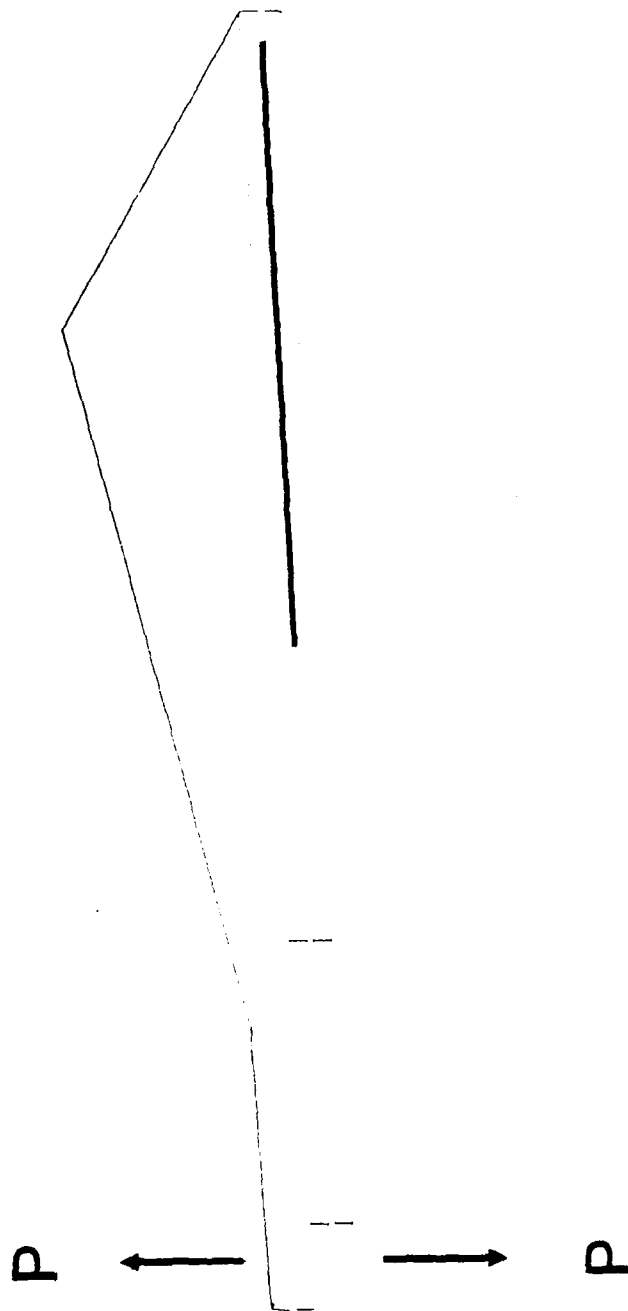


FIGURE 2

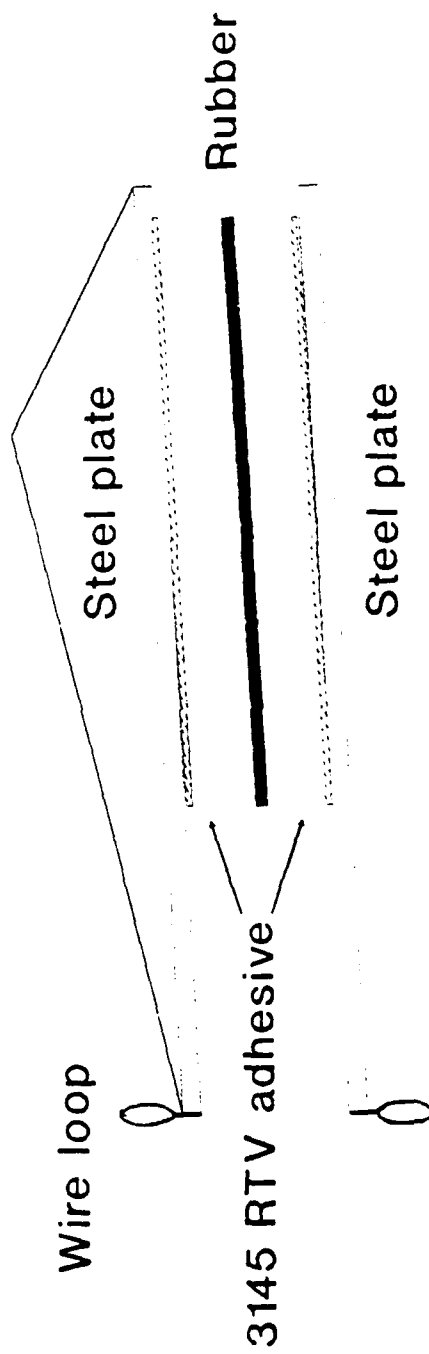


FIGURE 3

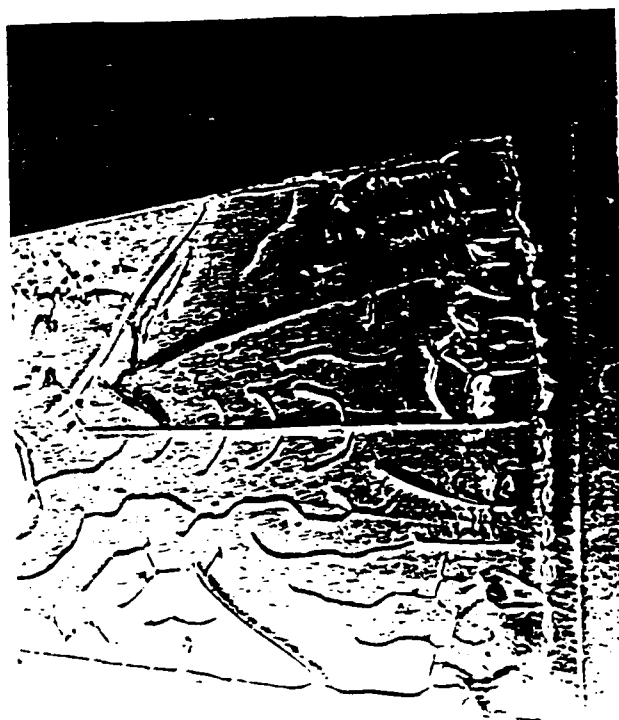


FIGURE 4

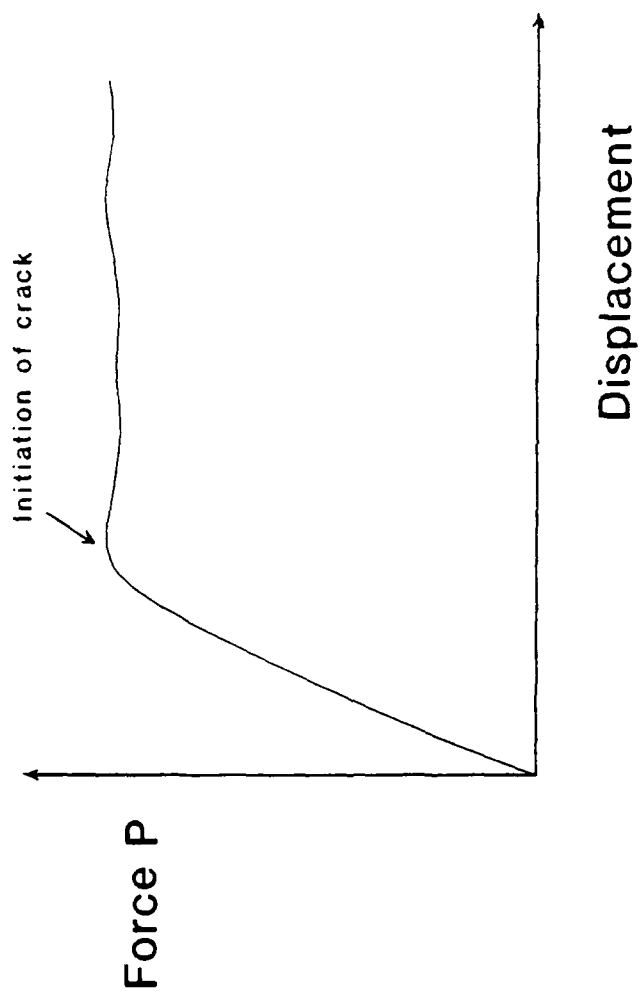


FIGURE 5

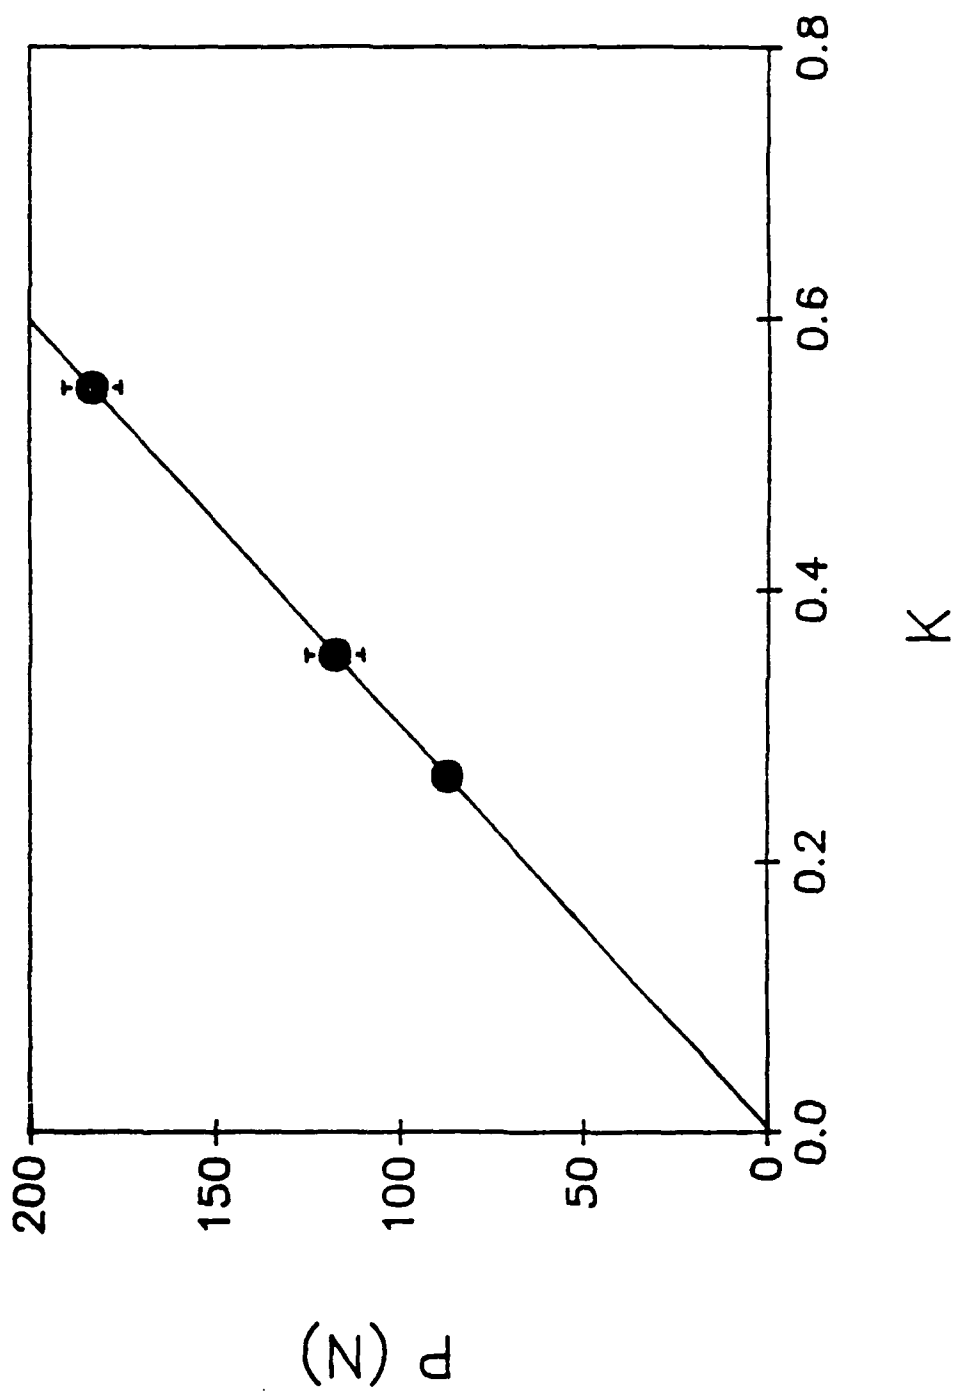


FIGURE 6

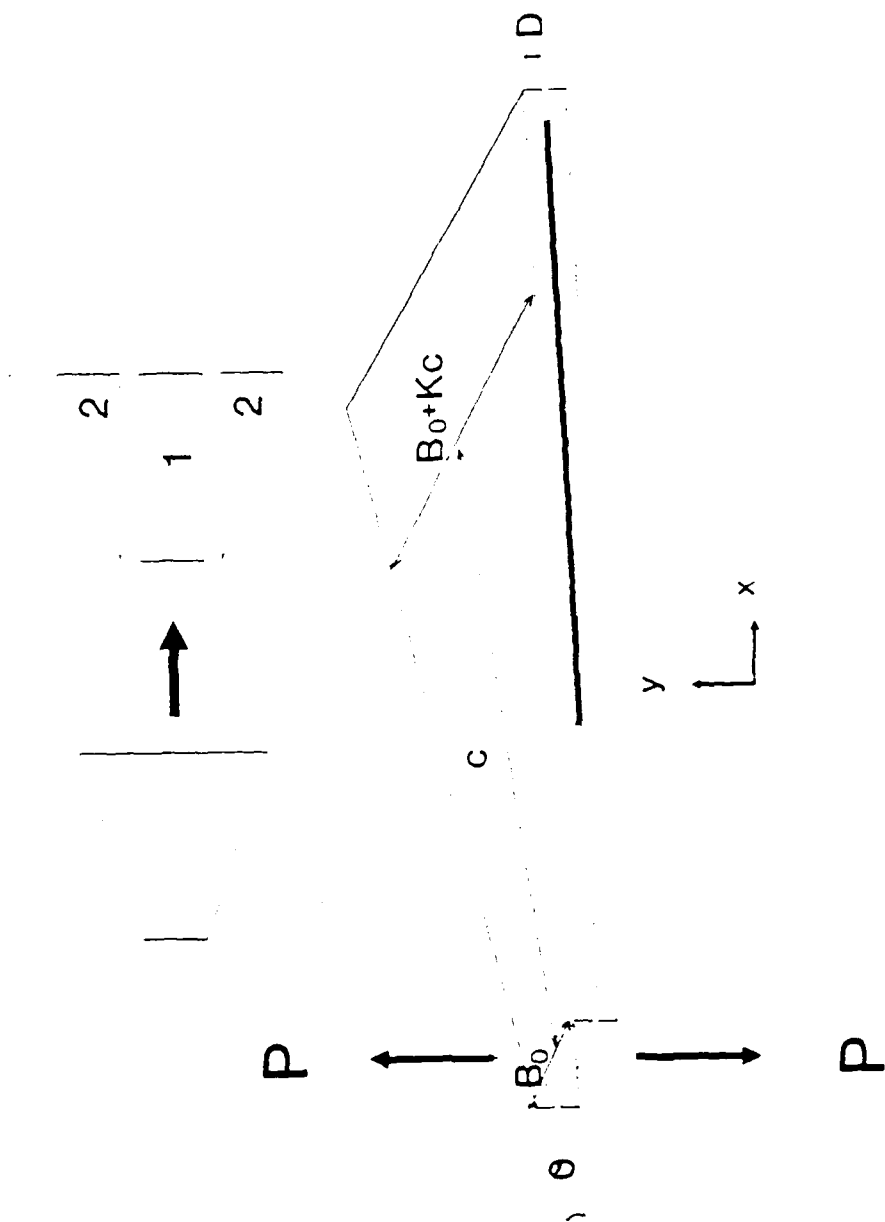


FIGURE 7

(DYN)

DISTRIBUTION LIST

Dr. R.S. Miller
Office of Naval Research
Code 432P
Arlington, VA 22217
(10 copies)

Dr. J. Pastine
Naval Sea Systems Command
Code 06R
Washington, DC 20362

Dr. Merrill K. King
Atlantic Research Corp.
5390 Cherokee Avenue
Alexandria, VA 22312

Dr. R.L. Lou
Aerojet Strategic Propulsion Co.
Bldg. 05025 - Dept 5400 - MS 167
P.O. Box 15699C
Sacramento, CA 95813

Dr. R. Olsen
Aerojet Strategic Propulsion Co.
Bldg. 05025 - Dept 5400 - MS 167
P.O. Box 15699C
Sacramento, CA 95813

Dr. Randy Peters
Aerojet Strategic Propulsion Co.
Bldg. 05025 - Dept 5400 - MS 167
P.O. Box 15699C
Sacramento, CA 95813

Dr. D. Mann
U.S. Army Research Office
Engineering Division
Box 12211
Research Triangle Park, NC 27709-2211

Dr. L.V. Schmidt
Office of Naval Technology
Code 07CT
Arlington, VA 22217

JHU Applied Physics Laboratory
ATTN: CPIA (Mr. T.W. Christian)
Johns Hopkins Rd.
Laurel, MD 20707

Dr. R. McGuire
Lawrence Livermore Laboratory
University of California
Code L-324
Livermore, CA 94550

P.A. Miller
736 Leavenworth Street, #6
San Francisco, CA 94109

Dr. W. Moniz
Naval Research Lab.
Code 6120
Washington, DC 20375

Dr. K.F. Mueller
Naval Surface Weapons Center
Code R11
White Oak
Silver Spring, MD 20910

Prof. M. Nicol
Dept. of Chemistry & Biochemistry
University of California
Los Angeles, CA 90024

Mr. L. Roslund
Naval Surface Weapons Center
Code R10C
White Oak, Silver Spring, MD 20910

Dr. David C. Sayles
Ballistic Missile Defense
Advanced Technology Center
P.O. Box 1500
Huntsville, AL 35807

(DYN)

DISTRIBUTION LIST

Mr. Geisler
ATTN: DY/MS-24
AFRPL
Edwards AFB, CA 93523

Naval Air Systems Command
ATTN: Mr. Bertram P. Sobers
NAVAIR-320G
Jefferson Plaza 1, RM 472
Washington, DC 20361

R.B. Steele
Aerojet Strategic Propulsion Co.
P.O. Box 15699C
Sacramento, CA 95813

Mr. M. Stosz
Naval Surface Weapons Center
Code R10B
White Oak
Silver Spring, MD 20910

MR. S.F. PALOPALI
THIOKOL CORP, ELKTON DIV.
P.O. BOX 241
ELKTON MD 21921

Dr. Grant Thompson
Morton Thiokol, Inc.
Wasatch Division
MS 240 P.O. Box 524
Brigham City, UT 84302

Dr. R.S. Valentini
United Technologies Chemical Systems
P.O. Box 50015
San Jose, CA 95150-0015

Dr. R.F. Walker
Chief, Energetic Materials Division
DRSMC-LCE (D), B-3022
USA ARDC
Dover, NJ 07801

Director
US Army Ballistic Research Lab.
ATTN: DRXBR-IBD
Aberdeen Proving Ground, MD 21005

Commander
US Army Missile Command
ATTN: DRSMI-RKL
Walter W. Wharton
Redstone Arsenal, AL 35898

Dr. Ingo W. May
Army Ballistic Research Lab.
ARRADCOM
Code DRXBR - IBD
Aberdeen Proving Ground, MD 21005

Dr. E. Zimet
Office of Naval Technology
Code 071
Arlington, VA 22217

Dr. Ronald L. Derr
Naval Weapons Center
Code 389
China Lake, CA 93555

Lee C. Estabrook, P.E.
Morton Thiokol, Inc.
P.O. Box 30058
Shreveport, Louisiana 71130

Dr. J.R. West
Morton Thiokol, Inc.
P.O. Box 30058
Shreveport, Louisiana 71130

Dr. D.D. Dillehay
Morton Thiokol, Inc.
Longhorn Division
Marshall, TX 75670

G.T. Bowman
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

(DYN)

DISTRIBUTION LIST

R.E. Shenton
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

Mike Barnes
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

Dr. Lionel Dickinson
Naval Explosive Ordnance
Disposal Tech. Center
Code D
Indian Head, MD 20340

Prof. J.T. Dickinson
Washington State University
Dept. of Physics 4
Pullman, WA 99164-2814

M.H. Miles
Dept. of Physics
Washington State University
Pullman, WA 99164-2814

Dr. T.F. Davidson
Vice President, Technical
Morton Thiokol, Inc.
Aerospace Group
3340 Airport Rd.
Ogden, UT 84405

Mr. J. Consaga
Naval Surface Weapons Center
Code R-16
Indian Head, MD 20640

Naval Sea Systems Command
ATTN: Mr. Charles M. Christensen
NAVSEA-62R2
Crystal Plaza, Bldg. 6, Rm 806
Washington, DC 20362

Mr. R. Beauregard
Naval Sea Systems Command
SEA 64E
Washington, DC 20362

Brian Wheatley
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

Mr. G. Edwards
Naval Sea Systems Command
Code 62R32
Washington, DC 20362

C. Dickinson
Naval Surface Weapons Center
White Oak, Code R-13
Silver Spring, MD 20910

Prof. John Deutch
MIT
Department of Chemistry
Cambridge, MA 02139

DAVID A. FLANIGAN, DIR. ADV. TECH
MORTON THIOKOL INC
AEROSPACE GROUP
2475 WASHINGTON BLVD.
OGDEN UT 84401

Dr. L.H. Caveny
Air Force Office of Scientific
Research
Directorate of Aerospace Sciences
Bolling Air Force Base
Washington, DC 20332

Dr. Donald L. Ball
Air Force Office of Scientific
Research
Directorate of Chemical &
Atmospheric Sciences
Bolling Air Force Base
Washington, DC 20332

(DYN)

DISTRIBUTION LIST

Dr. Anthony J. Matuszko
Air Force Office of Scientific Research
Directorate of Chemical & Atmospheric
Sciences
Bolling Air Force Base
Washington, DC 20332

Dr. Michael Chaykovsky
Naval Surface Weapons Center
Code R11
White Oak
Silver Spring, MD 20910

J.J. Rocchio
USA Ballistic Research Lab.
Aberdeen Proving Ground, MD 21005-5066

B. Swanson
INC-4 MS C-346
Los Alamos National Laboratory
Los Alamos, New Mexico 87545

Dr. James T. Bryant
Naval Weapons Center
Code 3205B
China Lake, CA 93555

Dr. L. Rothstein
Assistant Director
Naval Explosives Dev. Engineering Dept.
Naval Weapons Station
Yorktown, VA 23691

Dr. Henry Webster, III
Manager, Chemical Sciences Branch
ATTN: Code 5063
Crane, IN 47522

Dr. A.L. Slafkosky
Scientific Advisor
Commandant of the Marine Corps
Code RD-1
Washington, DC 20380

Dr. H.G. Adolph
Naval Surface Weapons Center
Code R11
White Oak
Silver Spring, MD 20910

U.S. Army Research Office
Chemical & Biological Sciences
Division
P.O. Box 12211
Research Triangle Park, NC 27709

Dr. John S. Wilkes, Jr.
FJSRL/NC
USAF Academy, CO 80840

Dr. H. Rosenwasser
AIR-320R
Naval Air Systems Command
Washington, DC 20361

Dr. Joyce J. Kaufman
The Johns Hopkins University
Department of Chemistry
Baltimore, MD 21218

Dr. A. Nielsen
Naval Weapons Center
Code 385
China Lake, CA 93555

(DYN)

DISTRIBUTION LIST

K.D. Pae
High Pressure Materials Research Lab.
Rutgers University
P.O. Box 909
Piscataway, NJ 08854

Prof. Edward Price
Georgia Institute of Tech.
School of Aerospace Engineering
Atlanta, GA 30332

Dr. John K. Dienes
T-3, B216
Los Alamos National Lab.
P.O. Box 1663
Los Alamos, NM 87544

Prof. R.W. Armstrong
University of Maryland
Dept. of Mechanical Engineering
College Park, MD 20742

A.N. Gent
Institute Polymer Science
University of Akron
Akron, OH 44325

Herb Richter
Code 385
Naval Weapons Center
China Lake, CA 93555

Dr. D.A. Shockey
SRI International
333 Ravenswood Ave.
Menlo Park, CA 94025

Dr. R.B. Kruse
Morton Thiokol, Inc.
Huntsville Division
Huntsville, AL 35807-7501

G.A. Zimmerman
Aeroject Tactical Systems
P.O. Box 13400
Sacramento, CA 95813

G. Butcher
Hercules, Inc.
P.O. Box 98
Magna, UT 84044

Prof. Kenneth Kuo
Pennsylvania State University
Dept. of Mechanical Engineering
University Park, PA 16802

W. Waesche
Atlantic Research Corp.
7511 Wellington Road
Gainesville, VA 22065

T.L. Boggs
Naval Weapons Center
Code 3891
China Lake, CA 93555

Dr. R. Bernecker
Naval Surface Weapons Center
Code R13
White Oak
Silver Spring, MD 20910

(DYN)

DISTRIBUTION LIST

Dr. C.S. Coffey
Naval Surface Weapons Center
Code R13
White Oak
Silver Spring, MD 20910

D. Curran
SRI International
333 Ravenswood Avenue
Menlo Park, CA 94025

E.L. Throckmorton
Code SP-2731
Strategic Systems Program Office
Crystal Mall #3, RM 1048
Washington, DC 23076

R.G. Rosemeier
Brimrose Corporation
7720 Belair Road
Baltimore, MD 20742

C. Gotzmer
Naval Surface Weapons Center
Code R-11
White Oak
Silver Spring, MD 20910

G.A. Lo
3251 Hanover Street
B204 Lockheed Palo Alto Research Lab
Palo Alto, CA 94304

R.A. SCHAPERY
DEPT. OF AEROSPACE ENGN.
UNIVERSITY OF TEXAS
AUSTIN TX 78712

Dr. Y. Gupta
Washington State University
Department of Physics
Pullman, WA 99163

J.M. Culver
Strategic Systems Projects Office
SSPO/SP-2731
Crystal Mall #3, RM 1048
Washington, DC 20376

Prof. G.D. Duvall
Washington State University
Department of Physics
Pullman, WA 99163

DR.G. LINDSAY
NAVAL WEAPONS CENTER
CODE 3858
CHINA LAKE CA 93555

Dr. M. Farber
135 W. Maple Avenue
Monrovia, CA 91016

W.L. ELBAN
DEPT. OF ELECTRICAL ENGN.
LOYOLA COLLEGE
4501 N. CHARLES STREET
BALTIMORE MD 21210

Defense Technical Information Center
Bldg. 5, Cameron Station
Alexandria, VA 22314
(12 copies)

Dr. Robert Polvani
National Bureau of Standards
Metallurgy Division
Washington, D.C. 20234

Director
Naval Research Laboratory
Attn: Code 2627
Washington, DC 20375
(6 copies)

MR. B. CONLEY
ONR RESIDENT REPRESENTATIVE
OHIO STATE UNIV. RES. FOUND.
1314 KINNEAR ROAD
COLUMBUS, OHIO 43212