

2

AD-A243 192



OFFICE OF NAVAL RESEARCH
Grant or Contract N00014-91WX-24155

DTIC
S
C
D

R&T Code 4134053

Technical Report No. 7

Evidence for Strong Electron-Phonon Coupling
in Thermal Conductivity of $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$

by

Joshua L. Cohn and Stuart A. Wolf
Naval Research laboratory
Washington, Dc 20375

and

T. A. Vanderah
Chemistry Division, Research Department
Naval Weapons Center, China Lake, CA 93555

Submitted for publication in
Phys. Rev. B., Rapid Commun.

October 1991

Reproduction in whole, or in part, is permitted for
any purpose of the United States Government.

This document has been approved for public release
and sale; its distribution is unlimited.

91-17384



91 1209 068

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank) 2. REPORT DATE Oct 91 3. REPORT TYPE AND DATES COVERED Technical Report #7 10/90-9/91

4. TITLE AND SUBTITLE Evidence for Strong Electron-Phonon Coupling in Thermal Conductivity of YBa₂Cu₃O_{7-δ} 5. FUNDING NUMBERS N00014-91WX-24155

6. AUTHORS Joshua L. Cohn, Stuart A. Wolf, and Terrell A. Vanderah

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Naval Weapons Center China Lake, CA 93555-6001 8. PERFORMING ORGANIZATION REPORT NUMBER

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research (Chemistry Program) 800 N. Quincy Street Arlington, VA 22217 10. SPONSORING/MONITORING AGENCY REPORT NUMBER

11. SUPPLEMENTARY NOTES Submitted to Phys. Rev. B. Rapid Commun.

12a. DISTRIBUTION /AVAILABILITY STATEMENT Approved for public release; distribution is unlimited. 12b. DISTRIBUTION CODE

13. ABSTRACT (Maximum 200 words)
We have measured the ab-plane thermal conductivity (κ) on single crystal YBa₂Cu₃O_{7-δ} ($\delta \approx 0.08$) in the temperature range $10 \text{ K} \leq T \leq 300 \text{ K}$. Our main focus is on analysis of the slope change in $\kappa(T)$ which occurs just below the superconducting transition. The reduced-temperature ($t=T/T_c$) derivative of the normalized thermal conductivity, $d(\kappa(5)/\kappa(n))/dt|_{t=1}$, as determined from the data, is rather small, ≤ 1.1 . From measurements of the electrical conductivity on the same specimens and application of the Wiedemann-Franz Law we determine the relative contributions to the heat conduction from the carriers and the lattice, and discuss the normal-state phonon scattering mechanisms. Employing these results we calculate the slope of the lattice thermal conductivity at T_c and infer that the slope of the carrier conductivity must be very large, ≥ 6 . This result implies strong coupling for some of the carriers.

14. SUBJECT TERMS 15. NUMBER OF PAGES 16. PRICE CODE

17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED 18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED 19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED 20. LIMITATION OF ABSTRACT

Evidence for Strong Electron-Phonon Coupling
in Thermal Conductivity of $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$

Joshua L. Cohn and Stuart A. Wolf

Naval Research Laboratory, Washington DC 20375

Terrell A. Vanderah

Naval Weapons Center, China Lake, CA 90124

Approved For	
NTIS GRA&I	
DTIC Tab	
Unannounced	
Justification	
By	
Distribution	
Availability Codes	
Avail and/or	
Dist	
A-1	
Special	

We have measured the ab-plane thermal conductivity (κ) on single crystal $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ ($\delta \approx 0.08$) in the temperature range $10\text{K} \leq T \leq 300\text{K}$. Our main focus is an analysis of the slope change in $\kappa(T)$ which occurs just below the superconducting transition. The reduced-temperature ($t=T/T_c$) derivative of the normalized thermal conductivity, $d(\kappa^s/\kappa^n)/dt|_{t=1}$, as determined from the data, is rather small, ≤ 1.1 . From measurements of the electrical conductivity on the same specimens and application of the Wiedemann-Franz Law we determine the relative contributions to the heat conduction from the carriers and the lattice, and discuss the normal-state phonon scattering mechanisms. Employing these results we calculate the slope of the lattice thermal conductivity at T_c and infer that the slope of the carrier conductivity must be very large, ≥ 6 . This result implies strong coupling for some of the carriers.

The thermal conductivity, κ , in the high- T_c superconductors¹ is unique in providing information on the transport mechanisms occurring in both the normal and superconducting states. The dominance of the phonon heat transport over that of the carriers and the importance of phonon-carrier scattering in the cuprates are manifested as a sharp upturn in the ab-plane κ for $T < T_c$. An analysis of this feature offers the potential of revealing information about the superconducting energy gap Δ and the strength of the electron-phonon coupling, two fundamental parameters which are currently the focus of much experimental and theoretical research.

In this paper we analyze the slope change in the ab-plane thermal conductivity of two $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ ($\delta \approx 0.08$) single crystals. Measurements of both the thermal and electrical conductivities on the same specimens enable us to estimate the carrier and lattice contributions to the total κ . The importance of phonon-phonon, phonon-carrier, and phonon-defect scattering are demonstrated. Employing these results we calculate the slope-change in the lattice conductivity at the superconducting transition. We infer that the carrier thermal conductivity decreases sharply below T_c , consistent with strong coupling for some of the carriers.

The $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (YBCO) crystals were grown in zirconia crucibles by a self-decanting flux method described elsewhere,² and were subsequently annealed in oxygen at 450-500°C. Both specimens were high-quality, mm-sized (80 μm -thick) single crystals with $\rho(295\text{K}) \approx 250 \mu\Omega \text{ cm}$, transition widths $\Delta T_c \leq 0.5\text{K}$, and $R=0$ at 92K.

The oxygen deficiency of specimen 1 was estimated as $\delta \sim 0.08$ from measurements of thermoelectric power, performed simultaneously with the thermal conductivity and reported previously.³ This value is consistent with the value inferred from the anomalous features in magnetization hysteresis loops, which have recently been shown⁴ to correlate with c-axis lattice parameter (a measure of oxygen content). The magnetization of specimen 2 implies an oxygen content similar to that of sample 1.

The thermal conductivity was measured using a steady-state technique, employing a differential chromel-constantan thermocouple and small resistive heater glued to the specimen with varnish. The temperature difference during measurement, ΔT , was typically 0.3K-1.0K. Linearity in the ΔT response was confirmed throughout the temperature range by varying the heater power. Errors in κ due to heat losses are estimated to be less than 2% except for $T > 200\text{K}$ where radiation losses become more significant. At room temperature we estimate an error in κ of $\sim 10\%$.

Figure 1 shows $\kappa(T)$ for both specimens. Near room temperature $\kappa \sim 8\text{-}9 \text{ W/mK}$, which agrees with previous measurements on single-crystal YBCO.⁵ The most notable feature in these data is the sharp upturn and peak that occur for $T < T_c$. This behavior is widely observed in the cuprates,¹ and arises from an increase in the phonon mean free path due to the reduced scattering of phonons by carriers as the latter condense into superconducting pairs. An analysis of this slope change is our

principal focus and is discussed in detail below. We first address the behavior of κ for $T > T_c$.

The contribution of the carriers to heat conduction may be calculated using the Wiedemann-Franz law (WFL), which states that $\kappa_e/\sigma T = L_0$, where κ_e is the electronic component of the thermal conductivity, σ is the electrical conductivity, and $L_0 = 2.45 \times 10^{-8}$ W Ω /K² is the Lorenz number. This yields an upper limit estimate of κ_e and we find at 100K, $\kappa_e/\kappa \approx 0.31$ for both specimens.

In Fig. 2 we plot the lattice conductivity, $\kappa_L = \kappa - \kappa_e$, where κ_e is determined, as above, from the measured electrical resistivity and the WFL. The slight upturn in κ_L at $T \leq 100$ K for specimen 2 is probably associated with superconducting fluctuations, an issue we address in more detail elsewhere.⁶ In general, we anticipate three principal sources of scattering for phonons in a metal: defects, free carriers, and other phonons. Phonon-carrier and phonon-defect scattering yield a temperature-independent or weakly decreasing κ_L with decreasing temperature at high temperatures.⁷ The observed decrease in κ_L with increasing T is characteristic of phonon-phonon scattering. The overall change in κ_L from 300K down to T_c is, for all specimens, relatively small ($\leq 20\%$) in comparison to that expected for a defect-free insulator ($\geq$ a factor of 3). Thus with regard to lattice conduction, YBCO appears to be in the complicated regime where all three scattering mechanisms are significant. These observations are consistent with a more quantitative analysis discussed below.

We now address the change in heat transport at the superconducting transition and consider the ratio of the thermal conductivities in the superconducting (s) and normal (n) states, κ^s/κ^n , a quantity which is most readily compared with theory. We may write the temperature derivative of this ratio as,

$$\frac{d}{dt} (\kappa^s/\kappa^n) = \eta \frac{d\alpha}{dt} + (1-\eta) \frac{d\beta}{dt} + \frac{d \ln \kappa^n}{dt}, \quad (1)$$

where $t=T/T_c$ is the reduced temperature, $\alpha=\kappa_s^s/\kappa_s^n$, $\beta=\kappa_L^s/\kappa_L^n$, and $\eta=\kappa_s^n/\kappa^n$ is the relative contribution of carriers to the total heat conduction. The normal-state thermal conductivity, κ^n , is determined, for $T < T_c$, from the experimental data by smooth extrapolation of the normal-state data to several degrees below T_c .⁸ In Fig. 3 we plot κ^s/κ^n versus t near $t=1$. The slopes are $d(\kappa^s/\kappa^n)/dt|_{t=1} = -0.4$ (sample 1) and -1.1 (sample 2) as indicated by the solid lines. The third term on the right-hand-side of (1) is determined directly from the data at $T \geq T_c$. This term is quite small and thus the slope is determined by a competition between the first two terms which have opposite sign.

The BCS theory of thermal conductivity for weak-coupling superconductors⁹⁻¹¹ predicts that, in the limiting cases of predominant electron-phonon and electron-defect scattering, respectively, α is a universal function of $\Delta/k_B T$ and for $\Delta=\Delta^{BCS}$, $d\alpha/dt|_{t=1} = 1.6$ (el-ph.) and 0 (el-def.). For strong coupling and when electron-defect scattering^{12,13} predominates, $d\alpha/dt|_{t=1} = 0$ as in weak coupling. The case of strong coupling and dominant

electron-phonon scattering is, however, much more complicated and depends on the form of the electron-phonon spectral function, $\alpha^2(\omega)F(\omega)$.¹⁴ For materials such as lead and mercury where these parameters are known from tunneling measurements, the very rapid decrease in κ , observed experimentally is in reasonable accord with theory. The difference from weak coupling arises both from the more rapid opening of the gap for strong coupling as well as the stronger frequency dependence of the quasiparticle relaxation rate.^{14,15} The value of $d\alpha/dt|_{t=1} = 9$ for lead¹⁶ is the largest known for any material. A slope $d\alpha/dt|_{t=1}$ substantially greater than 1.6 may thus be considered evidence for strong electron-phonon coupling.

The slope of the lattice conductivity for weak coupling and predominant phonon-electron scattering can be calculated from the BRT theory.¹⁰ Tewordt and Wölkhausen have modified this theory to include the effects of other scatterers¹⁷ and crystalline anisotropy¹⁸ on the lattice conductivity. In addition to the dependence on $\Delta/k_B T$, the slope $d\beta/dt|_{t=1}$ depends on the model phonon scattering rate, in the case of YBCO a rate which must, as discussed above, incorporate the combined effects of scattering by carriers, phonons, and defects. For strong coupling, the lattice conductivity very close to T_c can be calculated from the weak coupling theory, provided the BCS gap is scaled to the appropriate strong coupling value.¹⁸ Thus the temperature dependence of β in this regime is governed by $\Delta(T)$ which should follow the mean-field expression, $\Delta(T) = a(1-t)^{1/2}$, independent of

the coupling strength (a is a scaling constant $\approx 1.74\Delta(0)$ for the BCS gap)

It is important to note that the change in the lattice thermal conductivity at T_c generally reflects the coupling of carriers to longitudinal acoustic phonons (presumed responsible for most of the lattice heat conduction) and these phonons may not be the most important for superconductivity. Recent calculations by Peacor et al.¹⁹ suggest that the coupling for these modes in YBCO is rather weak. It is the value of $d\alpha/dt|_{t=1}$ which holds the most direct information regarding the strength of the carrier-phonon interaction relevant to superconductivity.

We now calculate the lattice conductivity slope from the BRT theory^{10,17,18} and place limits on the slope of the electronic component for YBCO using our experimental results and Eq. (1). The lattice conductivity is written as,²⁰

$$\kappa_L = \frac{k_B}{2\pi^2 v} \left(\frac{k_B T}{\hbar} \right)^3 \int_0^{\Theta/T} dx \frac{x^4 e^x}{(e^x - 1)^2} \int_0^1 d\zeta \frac{3}{2} (1 - \zeta^2) \tau(x, \zeta, T) \quad (2)$$

where $v = 5,000$ m/s is the sound velocity²¹, $\Theta = 400$ K is the Debye temperature²², $x = \hbar\omega/k_B T$ is the reduced phonon frequency, and $\tau(x, \zeta, T)$ is the phonon relaxation time. The scattering of phonons by crystal boundaries, point defects, carriers, and other phonons is represented by $\tau^{-1}(x, T) = v/d + A_{pd}(xT)^4 + A_{pc}xTg(x, T)(1 - \zeta^2)^{3/2} + A_{pp}x^2T^4$, where d is the crystallite thickness. Here, $g(x, T)$ is the ratio of the phonon-carrier scattering rates in the normal and superconducting states as defined by BRT, equal to

unity for $T > T_c$ and a universal function of $\Delta/k_B T$ for $T < T_c$. The integration over the variable ζ describes the anisotropy of the electron-phonon interaction; it is assumed that only the in-plane component of phonon momentum is emitted or absorbed by the carriers.¹⁸ Following reference 17 we take $\Delta = \chi \Delta^{BCS}$, where χ is a constant. The coefficients A_{pd} , A_{pe} , A_{pp} are determined self consistently by numerically integrating Eq. (2) to fit the normal-state κ_L data and the data for $T \leq 20K$ where $\kappa = \kappa_L$. The normal-state curves for the two specimens are shown as solid lines in Fig. 2. The slope $d\beta/dt|_{t=1}$ is then determined from the calculated $\beta(t)$ curves. In the inset of Fig. 3 we plot $-d\beta/dt|_{t=1}$ versus the gap size $2\Delta(0)/k_B T_c$ for the two parameter sets. A number of experiments suggest the existence of two gaps in YBCO, associated with the CuO_2 planes and Cu-O chains, with $2\Delta_{pl}(0)/k_B T_c \sim 5-6$ and $2\Delta_{ch}(0)/k_B T_c \sim 2.5-3.5$. The two-band expression¹³ for κ_L is more complicated than Eq. (2), but we may place a conservative lower limit on $d\beta/dt|_{t=1}$ by using the smallest gap size, $2\Delta(0)/k_B T_c = 2.5$. This implies $d\beta/dt|_{t=1} \sim -4.5$ which, from Eq. (1), yields $d\alpha/dt|_{t=1} \sim 6$. A more reasonable picture²³ that assigns strong coupling to the planes and weak coupling to the chains, would imply a plane contribution, $d\alpha^{pl}/dt|_{t=1} \sim 20$. Our main conclusion, $d\alpha/dt|_{t=1} \geq 6$, indicates that strong coupling characterizes some of the carriers in YBCO.

Since our analysis relies on the calculated value of $d\beta/dt|_{t=1}$, and specifically the choice of scattering parameters, we have examined the influence of the latter carefully. The

coefficients employed for sample 1 (2) imply that at $T=100\text{K}$ defect and carrier scattering account, respectively, for approximately 75% (60%) and 18% (30%) of the lattice thermal resistivity. Hence $d\beta/dt|_{T_c}$ is determined principally by the relative weights of the carrier and defect scattering terms. We find that $d\beta/dt|_{T_c}$ varies by less than 20% when these terms are varied within acceptable ranges. We also find similar results when we allow for a substantial deviation from the WFL, as would be expected for $T < \theta$ in a pure (electronically speaking) material' or a material with very strong electron-phonon coupling. Thus we believe that our overall conclusion regarding $d\alpha/dt|_{T_c}$ will survive a more detailed and specific model.

As mentioned above, in the context of the existing theory values of $d\alpha/dt|_{T_c}$ larger than 1.6 imply strong electron-phonon coupling and predominant electron-phonon scattering. Electron-phonon scattering predominates at T_c only in the purest of conventional materials and one may question whether it is feasible for this condition to hold in YBCO. The most obvious reason why it may be reasonable is the higher transition temperature of YBCO; the relative weight of phonons in the total scattering of carriers is substantially enhanced at higher temperatures. Secondly, the strength of the electron-phonon coupling may be substantially larger in YBCO than in any conventional material.

The slope $d\alpha/dt|_{T_c}$ for strong coupling and predominant electron-phonon scattering¹⁴ is directly proportional to the

product of the derivative, $d(\Delta/k_B)^2/dt|_{t=1}$ and a frequency average of the quasiparticle relaxation rate, $\Gamma(\omega)$. Employing the mean-field expression for the gap at T_c , a gap size of $2\Delta(0)/k_B T_c \approx 6$ would enhance $d(\Delta/k_B)^2/dt|_{t=1}$ by roughly a factor $(6/4.1)^2 \approx 2$ over that of lead, for example. It is generally true that the more strongly $\Gamma(\omega)$ decreases with frequency, the larger is the slope $d\alpha/dt|_{t=1}$. A strong frequency dependence can arise from sharply peaked structure in the coupling function, $\alpha^2(\omega)F(\omega)$. In this regard we note that there is substantial evidence from Raman scattering²⁴ that some carriers couple strongly to optical phonons, especially those modes yielding peaks in the phonon density of states $F(\omega)$ near energies of 15meV and 45meV. Recent tunneling results²⁵ on $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}$ reveal such structure in the derived coupling spectrum (with $\lambda \approx 3.5$), and similar results for YBCO are anticipated.²⁶ Thus it is possible that the contribution to $d\alpha/dt|_{t=1}$ from $\Gamma(\omega)$ is also large. As more information about $\alpha^2(\omega)F(\omega)$ becomes available it will be possible to examine these hypotheses in more quantitative fashion.

We thank S. D. Peacor for many fruitful discussions and for sharing calculations prior to publication. We also acknowledge valuable suggestions throughout this work from V. Z. Kresin, M. M. Miller, M. S. Osofsky, M. E. Reeves, and R. J. Soulen, Jr. One of the authors (J. L. C.) was supported by an Office of Naval Technology post-doctoral fellowship.

1. For a recent review of thermal conductivity in the cuprates, see C. Uher, J. Supercond. 3, 337 (1990)
2. T. A. Vanderah, et al., J. Crystal Growth, 1991.
3. J. L. Cohn et al., Electronic Structure and Mechanisms for High Temperature Superconductivity, ed. by J. Ashkenazi et al., (Plenum, New York, 1991).
4. M. S. Osofsky et al., unpublished.
5. S. J. Hagen, Z. Z. Wang, and N. P. Ong, Phys. Rev. B40, 9389 (1989); S. D. Peacor, J. L. Cohn, and C. Uher, Phys. Rev. B43, 8721 (1991).
6. J. L. Cohn, E. F. Skelton, and J. Z. Liu, unpublished.
7. See, e. g., R. Berman, Thermal Conduction in Solids, (Oxford, 1976), Ch. 8.
8. A monotonic behavior of κ^n for $T \leq T_c$ is confirmed by the work of Palstra et al. [Phys. Rev. Lett. 64, 3090 (1990)] where the thermal conductivity of a YBCO single crystal was measured in a field of 10 Tesla, sufficient to suppress T_c by about 5K.
9. B. T. Geilikman, Sov. Phys. JETP 7,721 (1958); see also B. T. Geilikman and V. Z. Kresin, Kinetic and Non-steady-State Effects in Superconductors (Wiley, New York, 1974).
10. J. Bardeen, G. Rickayzen, and L. Tewordt, Phys. Rev. 113, 982 (1959).
11. L. Tewordt, Phys. Rev. 129, 12 (1963); L. Tewordt, Phys. Rev. 129, 657 (1963).

12. See Geilikman and Kresin, reference 10.
13. B. J. Mrstik and D. M. Ginsberg, Phys. Rev. B5, 1817 (1972).
14. V. Ambegaokar and L. Tewordt, Phys. Rev. 134, A805 (1964); V. Ambegaokar and J. Woo, Phys. Rev. 139, A1818 (1965);
15. S. B. Kaplan et al., Phys. Rev. B14, 4854 (1976).
16. J. H. P. Watson and G. M. Graham, Can. J. Phys. 41, 1738 (1964).
17. L. Tewordt and Th. Wölkhausen, Sol. St. Commun. 70, 839 (1989).
18. L. Tewordt and Th. Wölkhausen, Sol. St. Commun. 75, 515 (1990).
19. S. D. Peacor et al., to be published, Phys. Rev. B, 1991.
20. It is implicitly assumed in the use of this integral equation that the relaxation-time approximation is valid. This means that Normal phonon-phonon collisions are neglected, a good approximation in crystals that are not too perfect (see, e.g. ref.7, Ch. 8).
21. See, e.g., P. B. Allen, Z. Fisk, and A. Migliori, in Physical Properties of High Temperature Superconductors, ed. by D. M. Ginsberg, (World Scientific, Teaneck, NJ, 1989), Vol. I, p. 213.
22. See, e.g., A. Junod in Physical Properties of High Temperature Superconductors, ed. by D. M. Ginsberg, (World Scientific, Teaneck, NJ, 1990), Vol. II, p. 13.
23. V. Z. Kresin and S. A. Wolf, Physica C169, 476 (1990).
24. See, e.g., C. Thomsen and M. Cardona, in reference 21, p. 409.

25. S. I. Vedeneev et al., submitted to Nature, 1991.
26. R. C. Dynes, in Proceedings of the Applied Superconductivity Conference, Snowmass, Colorado, September 1990 (in press).

Figure Captions

- Fig. 1 Thermal conductivity versus temperature for two YBCO single crystals.
- Fig. 2 Lattice conductivity (κ_L) versus temperature. κ_L was calculated by subtracting, from the data in Fig. 1, κ_0 as determined from the measured electrical resistivity and the WFL. The solid lines are calculated from Eq. (2) with $\Delta=0$ and parameters for sample 1 (2):
 $A_{pd}=1.73 \times 10^3$ (2.80×10^3) $s^{-1}K^{-4}$, $A_{pe}=6.0 \times 10^7$ (1.4×10^7) $s^{-1}K^{-1}$,
 $A_{pp}=40$ (19) $s^{-1}K^{-4}$ (see text for details).
- Fig. 3 The normalized thermal conductivity near T_c plotted versus reduced temperature. Inset: values of the the reduced-temperature derivative of the normalized lattice thermal conductivity, $d\beta/dt|_{t=1}$, plotted versus gap size, as calculated from Eq. (2) using the same parameters as for the normal-state curves in Fig. 2.

Fig. 1

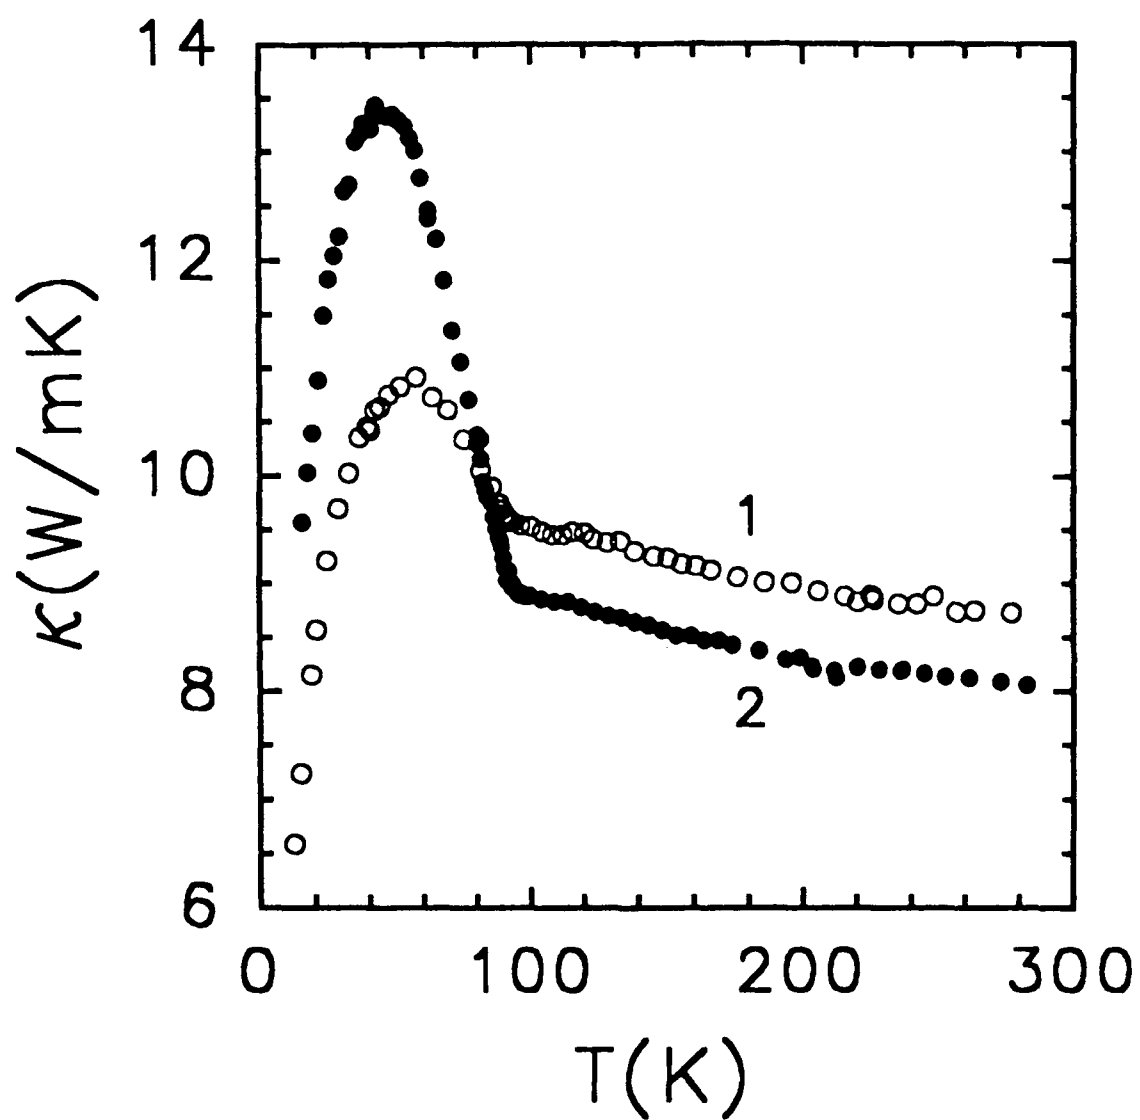


Fig. 2

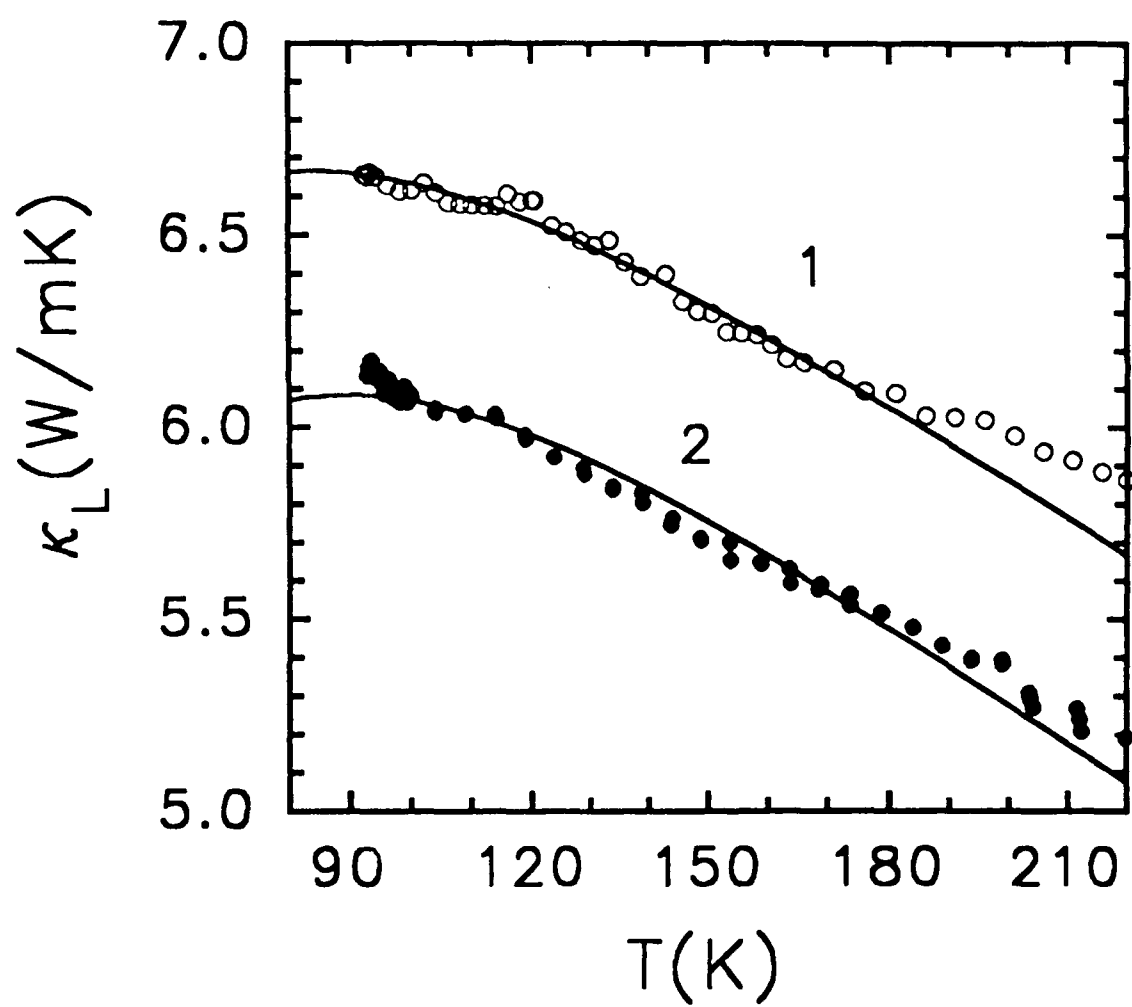


Fig. 3

