

REPC

AD-A251 283

Form Approved
OMB No. 0704-0188

(2)

Public reporting burden of this collection of information, including the gathering and maintaining the data needed for the collection of information, is estimated to be 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302.

Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE 05-15-92		3. REPORT TYPE AND DATES COVERED Technical 06-01-91 to 05-31-92	
4. TITLE AND SUBTITLE The Synthesis and Crystal Structure of Aluminum Selenite Trihydrate, $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$				5. FUNDING NUMBERS N00014-90-J-1159	
6. AUTHOR(S) W.T.A. Harrison, G.D. Stucky, R.E. Morris, and A.K. Cheetham					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of California Department of Chemistry Santa Barbara, CA 93106				8. PERFORMING ORGANIZATION REPORT NUMBER T10	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research Chemistry Program 800 N. Quincy Street Alexandria, VA 22217				10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES Prepared for Publication in Acta Crystallographica					
12a. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution unlimited				12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) Aluminum selenite trihydrate, synthetic, $M_r = 488.88$, trigonal, $R32$, $a = 8.3806$ (4) Å, $\alpha = 65.527$ (3)°, $V = 466.2$ Å ³ , $Z = 2$, $D_x = 3.48\text{g/cm}^3$, $\lambda(\text{Mo K}\alpha) = 0.71073$ Å, $\mu = 119.7\text{ cm}^{-1}$, $F(000) = 460$, $T = 298$ (2) K, $R = 4.48\%$, $R_w = 5.10\%$ for 556 observed reflections with $I > 3\sigma(I)$. Synthesized hydrothermally, $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$ consists of a 3-dimensional network of vertex-sharing octahedral AlO_6 and pyramidal SeO_3 groups, connected via Al-O-Se links. The three water molecules are coordinated by one of the aluminum atoms. The title compound is isostructural with $\text{Ga}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$ and $\text{Cr}_2(\text{SeO}_3)_3 \cdot \text{H}_2\text{O}$, and is closely related to aluminum selenite hexahydrate, $\text{Al}_2(\text{SeO}_3)_3 \cdot 6\text{H}_2\text{O}$.					
14. SUBJECT TERMS				15. NUMBER OF PAGES 12	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT UL		

OFFICE OF NAVAL RESEARCH

Contract N00014-90-J-1159
R&T Code 413n007

Technical Report No. 10

**The Synthesis and Crystal Structure of
Aluminum Selenite Trihydrate, $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$**

by

W.T.A. Harrison, G.D. Stucky, R.E. Morris, and A.K. Cheetham

Prepared for Publication in

Acta Crystallographica

May 15, 1992

Reproduction in whole or in part is permitted for any purpose of the United State Government.

This document has been approved for public release and sale; its distribution is unlimited.

This statement should also appear in Item 12 of the Report Documentation Page, Standard Form 298. Your contract number and R&T Code should be reported in Item 5 of Standard Form 298. Copies of the form are available from your cognizant grant or contract administrator.

**The Synthesis and Crystal Structure of
Aluminum Selenite Trihydrate, $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$**

William T. A. Harrison,* Galen D. Stucky,*
Russell E. Morris† and Anthony K. Cheetham†

Departments of Chemistry and Materials,†*
University of California,
Santa Barbara, CA 93106-9510, USA

Submitted to *Acta Crystallographica*, Section C

8/20/91



Requested For	
Crystal	☒
Other	☐
Microfilm	☐
Reproduction	☐
By	
Distribution/	
Availability Codes	
Avail and/or	
Dist Special	
A-1	

92-14079



92 5 28 028

Abstract. Aluminum selenite trihydrate, synthetic, $M_r = 488.88$, trigonal, $R32$, $a = 8.3806(4) \text{ \AA}$, $\alpha = 65.527(3)^\circ$, $V = 466.2 \text{ \AA}^3$, $Z = 2$, $D_x = 3.48 \text{ g/cm}^3$, $\lambda(\text{Mo K}\alpha) = 0.71073 \text{ \AA}$, $\mu = 119.7 \text{ cm}^{-1}$, $F(000) = 460$, $T = 298(2) \text{ K}$, $R = 4.48\%$, $R_w = 5.10\%$ for 556 observed reflections with $I > 3\sigma(I)$. Synthesized hydrothermally, $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$ consists of a 3-dimensional network of vertex-sharing octahedral AlO_6 and pyramidal SeO_3 groups, connected *via* Al–O–Se links. The three water molecules are coordinated by one of the aluminum atoms. The title compound is isostructural with $\text{Ga}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$ and $\text{Cr}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$, and is closely related to aluminum selenite hexahydrate, $\text{Al}_2(\text{SeO}_3)_3 \cdot 6\text{H}_2\text{O}$.

Introduction: In the solid-state, the selenium(IV)-containing selenite ion, SeO_3^{2-} shows a characteristic pyramidal coordination due to its (unobserved) $4s^2$ hybridized lone pair of electrons. As yet, there are few well defined structural families of selenites, but a number of phases containing a trivalent, octahedral metal ion, M^{3+} , selenite, SeO_3^{2-} and/or hydrogen selenite HSeO_3^- , and possibly water, have been studied by single crystal X-ray diffraction methods, including: $\text{Mn}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$ (Koskenlinna and Valkonen, 1977); $\text{FeH}(\text{SeO}_3)_2$ (Valkonen and Koskenlinna, 1978); $\text{Sc}(\text{HSeO}_3)_3$ (Valkonen and Leskelä, 1978); $\text{Ga}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$ Rastsvetaeva, Andrianov and Volodnia, 1986); $\text{Fe}(\text{Se}_2\text{O}_5)(\text{HSeO}_3)$ and $\text{Fe}(\text{HSeO}_3)_3$ (Muilu and Valkonen, 1987); $\text{Al}_2(\text{SeO}_3)_3 \cdot 6\text{H}_2\text{O}$ and $\text{Al}(\text{SeO}_3)(\text{HSeO}_3) \cdot 2\text{H}_2\text{O}$ (Morris, Harrison, Stucky and Cheetham, 1991); and $\text{Cr}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$ and $\text{InH}(\text{SeO}_3)_2$ (Harrison, McManus, Stucky and Cheetham, 1991). Here we report the preparation and crystal structure of $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$.

Experimental: The title compound was synthesised hydrothermally from the starting materials $\text{Al}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ (Fisher, 2 g) and excess SeO_2 (Aldrich, 5 g) in 15 cm^3 of water. The teflon-lined steel bomb was heated to 473(5) K for 48 hours and cooled to room temperature overnight. An estimated maximum pressure of 3 MPa was achieved. Transparent, rhombic crystals with linear dimensions of up to 0.5 mm were recovered from the reaction mixture.

An irregular crystal, dimensions *ca.* $0.12 \times 0.12 \times 0.12 \text{ mm}$ was mounted on a Huber automated diffractometer. The unit cell constants were determined and refined from 14 centered reflections ($18^\circ < 2\theta < 24^\circ$). Data were collected at room temperature (298(2) K) in the θ - 2θ scan mode (scan speed = 6° min^{-1}) using graphite monochromated $\text{Mo K}\alpha$ radiation ($\lambda = 0.71073 \text{ \AA}$) over the range $0 < 2\theta \leq 65^\circ$ for $-6 \leq h \leq 9$, $-5 \leq k \leq 10$, $1 \leq l \leq 12$, $(\sin\theta/\lambda)_{\text{max}} = 0.76$), with regular checks on reflection intensity (every 100 reflections; no variation observed), absorption correction based on ψ -scans of reflections

with $\chi \sim 90^\circ$ (min. 1.0, max. 1.2) applied during data reduction. There were no systematic absences, consistent with five distinct trigonal space groups: $R3$, $R\bar{3}$, $R32$, $R3m$ and $R\bar{3}m$. 2293 reflections were measured, of which 556 were used in the structure solution and refinement (merging $R = 6.6\%$; reflections with $I < 3\sigma(I)$ considered unobserved).

The initial model, in the rhombohedral setting of space group $R32$ (No. 155), was taken from our study of the isostructural chromium selenite trihydrate (Harrison, McManus, Stucky and Cheetham, 1991), and the usual atomic positional and anisotropic thermal parameters were refined to convergence. For the final cycle of full matrix anisotropic refinement against F : 53 parameters, origin defined as centroid of structure (Waser, 1974), $\Sigma(\text{shift}/\text{e.s.d.}) = 0.01$, $R = 4.48\%$, $wR = 5.10\%$ (3-term Chebyshev weighting scheme (Carruthers and Watkin, 1979) with coefficients 24(6), -11(7) and 11(5) where the digit in parentheses is the e.s.d.), maximum residual electron density = $2 \text{ e } \text{\AA}^{-3}$ near O(4), no proton positions located. Structure refinement and analysis was carried out using the Oxford CRYSTALS system (Watkin, Carruthers and Betteridge, 1985) on a $\mu\text{VAX-II}$ computer. Complex, neutral-atom scattering-factors were taken from *International Tables for X-Ray Crystallography* (1974). An isotropic secondary extinction correction (Larson, 1970: refined value = 46(4)) was also applied.

Discussion: Table 1* gives final atomic positional and thermal parameters for $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$, and Table 2 gives selected bond distance/angle data for this phase. The structure of aluminum selenite trihydrate (Figure 1) consists of a 3-dimensional network of vertex-sharing AlO_6 and SeO_3 groups linked *via* Al-O-Se bonds: there are two crystallographically-distinct aluminum atoms, one selenium atom and four oxygen atoms, one of which (O(4)) is a water molecule. Both aluminum atoms form typical octahedral coordination with oxygen ($d_{\text{ave}}(\text{Al}(1)\text{-O}) = 1.945(6) \text{ \AA}$, $d_{\text{ave}}(\text{Al}(2)\text{-O}) = 1.902(6) \text{ \AA}$), the selenium atom ($d_{\text{ave}}(\text{Se-O}) = 1.711(5) \text{ \AA}$; $\theta_{\text{ave}}(\text{O-Se-O}) = 96.4(3)^\circ$) is pyramidal, and three of

the four oxygen atoms form Al-O-Se bridges ($\theta_{\text{ave}} = 124.7(3)^\circ$). The selenite ion geometry compares well with the average values ($\langle d(\text{Se-O}) \rangle = 1.709(10) \text{ \AA}$, $\langle \theta(\text{O-Se-O}) \rangle = 100.2(1.3)^\circ$; values in parentheses = r.m.s. deviations) recently derived by Hawthorne, Groat and Ercit (1987) for a large number of (H)SeO₃ species.

The structure of Al₂(SeO₃)₃·3H₂O consists of stacks of alternating Al(1) and Al(2) octahedra in the rhombohedral [111]-direction. Each Al(1) octahedron is linked to its nearest Al(2) neighbor by three different Al(1)-O(3)-Se(1)-O(2)-Al(2) links, thus forming an empty 'cage', centered at approximately ($\frac{1}{3}, \frac{1}{3}, \frac{1}{3}$). The three O(1)s around Al(1) are also bonded to Se(1), thus adjacent octahedra of Al(1) are crosslinked by Al(1)-O(1)-Se(1)-O(3)-Al(1)' and Al(1)-O(1)-Se(1)-O(2)-Al(2) links, building up an infinite network of octahedra and pyramids. Al₂(SeO₃)₃·3H₂O is isostructural with Ga₂(SeO₃)₃·3H₂O (Rastsvetayeva, Andrianov and Volodnia, 1986) and Cr₂(SeO₃)₃·3H₂O (Harrison, McManus, Stucky and Cheetham, 1991).

Two other aluminum selenite hydrate phases have been characterized by X-ray single crystal methods: Al₂(SeO₃)₃·6H₂O (AlSeO-I) and Al(SeO₃)(HSeO₃)·2H₂O (AlSeO-II), which were also prepared under mild hydrothermal conditions (Morris, Harrison, Stucky and Cheetham, 1991), indicating the wealth of new systems accessible by these methods by subtle variation of reactant concentrations, pH and temperature. Both AlSeO-I and AlSeO-II contain 3-dimensional networks of octahedral aluminum cations and pyramidal selenium species, and both also contain Al-OH₂ links as part of the aluminum atom coordination. AlSeO-II has a quite different structure to Al₂(SeO₃)₃·3H₂O, but AlSeO-I is closely related to the phase described here, and contains octahedral AlO₆ stacks joined by a similar triad of Al-O-Se-O'-Al' bonds surrounding an empty cavity. However, in AlSeO-I, compared to Al₂(SeO₃)₃·3H₂O, each terminal aluminum is coordinated to three waters as well the three oxo-selenium bridges to its neighbor. As opposed to Al₂(SeO₃)₃·3H₂O, the third


Se-O vertex in AlSeO-I only partakes in H-bonds and is not associated with another aluminum cation. Thus 'molecular' units of $\text{Al}_2(\text{SeO}_3)_3 \cdot 6\text{H}_2\text{O}$ make up the repeating *motif* in AlSeO-I; in $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$, three water molecules are eliminated, adjacent octahedral stacks shift relative to each other to form the Al-O-Se-O-Al crosslinking bonds described above, and a 3-dimensional, as opposed to molecular structure results. Investigation into related selenite phases is ongoing.

Acknowledgements: We thank Nancy Keder (UCSB) for crystallographic assistance. REM thanks the SERC for a studentship. This work was supported by the Office of Naval Research (GDS).

* Lists of observed and calculated structure factors and anisotropic thermal parameters have been deposited with the British Library Document Supply Center as Supplementary Publication No. (5 pp.). Copies may be obtained through The Technical Editor, International Union of Crystallography, 5 Abbey Square, Chester, CH1 2HU, England.

Figure Caption.


Figure 1: Detail of the crystal structure of $\text{Al}_2(\text{SeO}_3)_3 \cdot 3\text{H}_2\text{O}$ showing the atomic labelling scheme and the linkage of Al(1) and Al(2) octahedra *via* selenite bridges. O(4) is a water molecule.

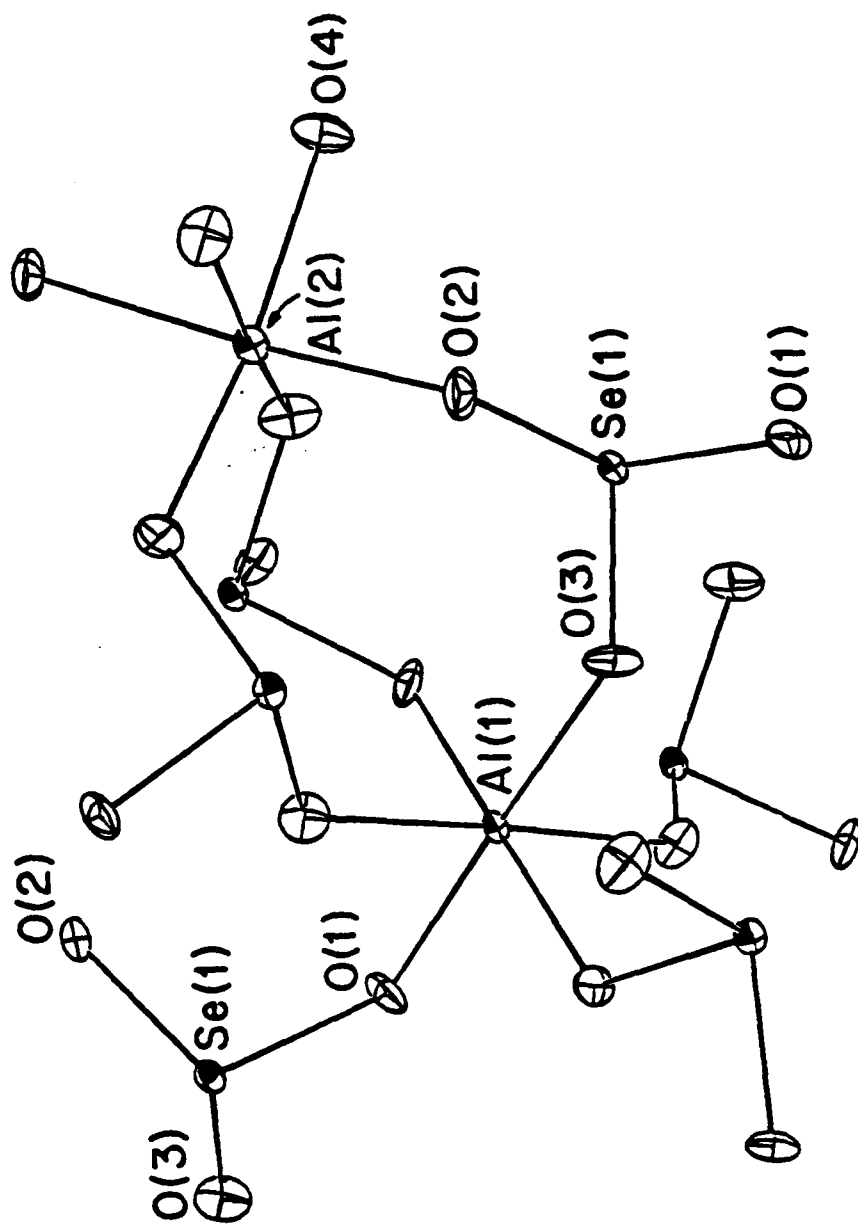

References

- CARRUTHERS, J. R. AND WATKIN, D. J. (1979), *Acta Crystallogr.* A35, 698-699.
- HARRISON, W. T. A.; MCMANUS, A. V. P., STUCKY, G. D. AND CHEETHAM, A. K. (1991) *Eur. J. Sol. St. Inorg. Chem.* submitted for publication.
- HAWTHORNE, F. C., GROAT, L. A. AND ERCIT, T. S. (1987) *Acta Crystallogr.* C43, 2042-2044.
- International Tables for X-Ray Crystallography*, (1974) Vol IV, Kynoch Press, Birmingham, UK.
- KOSKENLINNA, M. AND VALKONEN., J. (1977) *Acta Chem. Scand.* A31, 611-614.
- LARSON, A. C. In *Crystallographic Computing*; Ahmed, F. R., Ed.; Munksgaard: Copenhagen, 1970; p291.
- MORRIS, R. E., HARRISON, W. T. A., STUCKY G. D. AND CHEETHAM, A. K. (1991) *J. Sol. St. Chem.* in press.
- MUILU, H. AND VALKONEN, J. (1987) *Acta Chem. Scand.* A41, 183-189.
- RASTSVETAeva, R. K., ANDRIANOV, V. I. AND VOLODNIA, A. N. (1986) *Dokl. Akad. Nauk SSSR.* 291, 352-353.
- VALKONEN, J. AND KOSKENLINNA, M. (1978) *Acta Chem. Scand.* A32, 603-606.
- VALKONEN, J. AND LESKELÄ, M. (1978) *Acta Crystallogr.* B34, 1323-1326.
- WASER, J. (1974) *Acta Crystallogr.* A30, 261-264.
- WATKIN, D. J., CARRUTHERS, J. R. AND BETTERIDGE, P. W., (1985), *CRYSTALS User Guide*. Chemical Crystallography Laboratory, Oxford University, UK.

Table 1: Atomic Positional Parameters




Atom	x	y	z	U_{equiv}
Al(1)	0.2048 (3)	0.2048 (3)	0.2048 (3)	0.0052
Al(2)	0.4398 (3)	0.4398 (3)	0.4398 (3)	0.0088
Se(1)	0.9188 (2)	0.5458 (2)	0.0086 (2)	0.0067
O(1)	0.848 (1)	0.594 (1)	0.504 (1)	0.0109
O(2)	0.204 (1)	0.542 (1)	0.423 (1)	0.0136
O(3)	0.405 (1)	0.310 (1)	0.056 (1)	0.0125
O(4)†	0.458 (1)	0.690 (1)	0.357 (1)	0.0144

†water molecule

$$U_{\text{equiv}} = \frac{1}{3} \sum_i \sum_j U_{ij} a_i^* a_j^* a_i a_j$$

Table 2: Bond Distances(Å)/Angles(°)



Al(1)–O(1)	1.958(8) × 3	Al(1)–O(3)	1.932(8) × 3
Al(2)–O(2)	1.836(8) × 3	Al(2)–O(4)	1.967(8) × 3
Se(1)–O(1)	1.699(7)	Se(1)–O(2)	1.754(8)
Se(1)–O(3)	1.679(7)		
O(1)–Al(1)–O(1)	91.5(4) × 3	O(3)–Al(1)–O(1)	87.6(3) × 3
O(3)–Al(1)–O(1)	86.6(3) × 3	O(3)–Al(1)–O(1)	177.9(4) × 3
O(3)–Al(1)–O(3)	94.3(4) × 3		
O(2)–Al(2)–O(2)	94.1(4) × 3	O(4)–Al(2)–O(2)	88.1(3) × 3
O(4)–Al(2)–O(2)	173.8(5) × 3	O(4)–Al(2)–O(2)	91.5(4) × 3
O(4)–Al(2)–O(4)	86.0(4) × 3		
O(2)–Se(1)–O(1)	100.5(4)	O(3)–Se(1)–O(1)	89.8(4)
O(3)–Se(1)–O(2)	98.8(4)		
Se(1)–O(1)–Al(1)	122.7(4)	Se(1)–O(2)–Al(2)	124.4(4)
Se(1)–O(3)–Al(1)	127.1(5)		

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)*
Chemistry Division, Code 1113
800 North Quincy Street
Arlington, Virginia 22217-5000

Dr. James S. Murday (1)
Chemistry Division, Code 6100
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. Robert Green, Director (1)
Chemistry Division, Code 385
Naval Air Weapons Center
Weapons Division
China Lake, CA 93555-6001

Dr. Elek Lindner (1)
Naval Command, Control and Ocean
Surveillance Center
RDT&E Division
San Diego, CA 92152-5000

Dr. Bernard E. Douda (1)
Crane Division
Naval Surface Warfare Center
Crane, Indiana 47522-5000

Dr. Richard W. Drisko (1)
Naval Civil Engineering
Laboratory
Code L52
Port Hueneme, CA 93043

Dr. Harold H. Singerman (1)
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Dr. Eugene C. Fischer (1)
Code 2840
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Defense Technical Information
Center (2)
Building 5, Cameron Station
Alexandria, VA 22314

* Number of copies to forward