

AD-A253 659



2

OFFICE OF NAVAL RESEARCH

Contract N00014-82K-0612

R&T CODE: 4133032

TECHNICAL REPORT NO. 74

Optical Properties of Composite Membranes Containing Arrays of
Nanoscopic Gold Cylinders

by

C. A. Foss, Jr., G. L. Hornyak, J. A. Stockert
and C. R. Martin

Prepared for publication

in

Journal of Physical Chemistry

Department of Chemistry
Colorado State University
Ft. Collins, CO 80523

July 20, 1992

DTIC
ELECTE
JUL 31 1992
S B D

Reproduction in whole or part is permitted for
any purpose of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited

92 7 28 068

92-20412



REPORT DOCUMENTATION PAGE

OMB No 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188) Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE 7-20 - 1992		3. REPORT TYPE AND DATES COVERED Interim	
4. TITLE AND SUBTITLE Optical Properties of Composite Membranes Containing Arrays of Nanoscopic Gold Cylinders				5. FUNDING NUMBERS Contract # N00014-82K-0612	
6. AUTHOR(S) C. A. Foss, Jr., G. Louis Hornyak, J. A. Stockert and Charles R. Martin					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Dr. Charles R. Martin Department of Chemistry Colorado State University Fort Collins, CO 80523				8. PERFORMING ORGANIZATION REPORT NUMBER ONR TECHNICAL REPORT # 74	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research 800 North Quincy Street Arlington, VA 22217				10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES					
12a. DISTRIBUTION / AVAILABILITY STATEMENT Reproduction in whole or part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.				12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) Nano-chemistry, physics and materials are important and evolving fields in modern science. One of the most interesting aspects of nanomaterials concerns the optical properties of nanoscopic metal particles. While bulk metals are optically opaque, effective medium theory (EMT) predicts that collections of small metal particles can be transparent, provided that the wavelength of light employed is much greater than a characteristic dimension of the particle. Hence, EMT can be used as a guide to prepare metal-containing composites that are both electronically conductive and optically transparent. We have recently shown that composites of this type can be prepared by electrochemical deposition of metals within the pores of a microporous "template" membrane. In this report we show for the first time that composite membranes prepared via this "template" route can be optically transparent throughout the near infrared (NIR) and into the visible region of the electromagnetic spectrum. Furthermore, we show that by changing the shapes of the particles prepared, the color of the composite membrane can be reproducibly and predictably varied. Finally, we show that these results are in general agreement with the predictions of the appropriate formulation of EMT.					
14. SUBJECT TERMS Transparent metals, nano materials, effective medium theory				15. NUMBER OF PAGES	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED		20. LIMITATION OF ABSTRACT	

**Optical Properties of Composite Membranes Containing
Arrays of Nanoscopic Gold Cylinders**

Colby A. Foss, Jr., Gabor L. Hornyak, Jon A. Stockert,
and Charles R. Martin*

Department of Chemistry, Colorado State University
Fort Collins, Colorado 80523

*Author to whom correspondence should be addressed

ABSTRACT

Arrays of nanoscopic Au cylinders were prepared by electrochemical deposition of Au within the pores of nanoporous (pore diameter = 50 nm) alumina template membranes. We show, for the first time, that the Au/alumina composite membranes obtained can be optically transparent into the visible portion of the electromagnetic spectrum. We also show that by changing the aspect ratio of the Au nanocylinders prepared, the color of the composite membrane can be reproducibly and predictably varied. Finally, we show that these results are in agreement with the predictions of Maxwell-Garnett theory for metal-insulator composites.

Accession For	
NTIS GRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

DTIC QUALITY INSPECTED 5

Nano- chemistry [1], physics [2] and materials [3] are important and evolving fields in modern science. One of the most interesting aspects of nanomaterials concerns the optical properties of nanoscopic metal particles. While bulk metals are optically opaque, effective medium theory (EMT) [4] predicts that collections of small metal particles can be transparent, provided that the wavelength of light employed is much greater than a characteristic dimension of the particle [4]. Hence, EMT can be used as a guide to prepare metal-containing composites that are both electronically conductive and optically transparent [5-8]. Such composites are inherently interesting from a purely scientific viewpoint and have a variety of possible technological applications [7].

We have recently shown that composites of this type can be prepared by electrochemical deposition of metals within the pores of a microporous "template" membrane [8]. However, the metal particles investigated in our prior work were large (of diameters greater than 200 nm). As a result, the composite membranes were transparent in the infrared (IR) portion of the electromagnetic spectrum but opaque in the near IR (NIR) and visible regions. Our goal, since publishing this work [8] has been to push this optical transparency into the visible portion of the spectrum. In order to accomplish this objective we synthesized alumina template membranes [9,10] with much smaller pore diameters than the membranes used in our previous work. We also modified the electrochemical methods used to deposit the metal particles in these "nanoporous" alumina membranes [10].

In this report we show for the first time that the Au/alumina composites obtained by depositing Au into these nanoporous template membranes can be optically transparent throughout the NIR and into the visible region of the electromagnetic spectrum. Furthermore, we show for

the first time that by changing the shapes of the particles prepared, the color of the composite membrane can be reproducibly and predictably varied. Finally, we show that these results are in agreement with the predictions of the appropriate formulation of EMT.

The alumina template membranes were prepared electrochemically from Al metal [9,10]. The details of the membrane syntheses will be given in [10]. These membranes contain cylindrical pores of uniform diameter [8-10]. Membranes with pore diameters of 50 nm were prepared for these studies. A transmission electron micrograph (TEM) of a typical membrane is shown in Figure 1A; the pore diameters were evaluated from such micrographs. Au microcylinders were deposited within the pores using a modified form [10] of the electrochemical method described in our previous work [8]. The diameters of these cylinders is determined by the diameter of the pores in the membrane; the aspect ratio is determined by the quantity of metal deposited. Figure 1B shows a TEM of a cross section of a template membrane after deposition of the Au microcylinders. In this case the cylinders are 50 nm in diameter and 500 nm in length (aspect ratio = 10). A related electrochemical method has been used to prepare composites for selective absorption of solar energy [11]. However, particles with known aspect ratios could not be obtained via this earlier method [11].

The ability to reproducibly and predictably control both the diameter and aspect ratio of the metal microcylinders prepared is an important feature of the template method. Furthermore, the template method yields metal particles which are completely isolated from each other, with uniform lateral separation distances. Finally, the template synthesized metal particles are oriented in the same direction in space (Figure 1B). As we shall see, all of

these features are critical in determining the optical properties of these Au/alumina composite membranes.

Figure 2 shows a transmittance spectrum of a composite containing Au cylinders that are 50 nm in diameter and approximately 50 nm in length (aspect ratio = 1). This composite is substantially transparent throughout the NIR and into the visible portion of the spectrum. This is the first time that transparency to such short wavelengths of light has been demonstrated for template-synthesized metal particles. Note further that a strong absorption band is observed near the plasma frequency of Au [12].

Figure 3 shows a close-up of the plasma band for composites containing Au particles with two different aspect ratios - for Curve A the particles are 50 nm in diameter and 50 nm in length; for Curve B the particles are also 50 nm in diameter, but are ca. 300 nm in length. The plasma band for the long narrow cylinders is blue-shifted relative to the plasma band for the cylinders with an aspect ratio of unity. As a result, **the color of the composite varies with the shape of the Au particles within the membrane.** The membrane corresponding to Curve A transmits a blue-purple color; the membrane corresponding to Curve B is deep red in color. While this affect of particle aspect ratio on optical properties has been treated theoretically [11], to our knowledge, this is the first time that this aspect ratio-color dependence has been demonstrated experimentally.

All of these observations - the high optical transparency, the strong plasma absorption and, most importantly, the change in color with particle shape - are predicted by the Maxwell-Garnett (M-G) formulation of EMT [4]. According to M-G theory, the dielectric function of the composite membrane, ϵ , containing nanoscopic metal particles is related to the dielectric functions of the metal, ϵ_m , and the host membrane, ϵ_0 , via [4]

$$\frac{\epsilon - \epsilon_0}{\epsilon + \kappa\epsilon_0} = f_m \frac{\epsilon_m - \epsilon_0}{\epsilon_m + \kappa\epsilon_0} \quad (1)$$

where f_m is the volume fraction occupied by the metal particles and κ is a “screening” parameter that depends on the shape of the particles [4,5]. Spherical particles have $\kappa = 2$, whereas long, needle-like particles aligned with their principal axes parallel to the direction of light incidence have $\kappa = 1$ [5]; these values of κ are of interest to the work described here because the Au particles with aspect ratio = 10 approach the long, needle-like limiting case, and the particles with an aspect ratio of unity can be treated as spheres.

Equation 1 can be used to simulate absorption spectra for our Au/alumina composites. Figure 4 shows simulated absorption spectra for composites containing spherical (Curve A) and needle-like (Curve B) particles. In agreement with the experimental observations (Figures 2 and 3), these simulated spectra show that the composites are highly transparent at energies below the plasma absorption band. Furthermore, the plasma absorption maximum for the needle-like particles ($\kappa = 1.2$) is blue shifted relative to the maximum for spherical particles ($\kappa = 2$). Hence, this simple theoretical analysis explains the experimentally-observed change in color of the composite membranes with the shape of the Au particles.

The template method allows for precise control over size, shape and orientation of metallic (and polymeric [13]) particles produced within the porous membrane. We are especially interested in preparing particles with even smaller diameters because the extent of transparency to visible light should be further improved. We are also investigating applications of such

arrays of small metal particles in surface enhanced absorption and Raman spectroscopies, chemical catalysis, and chemical sensors.

Acknowledgements:

This work was supported by the Office of Naval Research

References:

1. Whitesides, G.M.; Mathias, J.P.; Seto, C.T. *Science*, 1991, 254, 1312.
2. Sundaram, M.; Chalmers, S.A.; Hopkins, P.F.; Gossard, A.C. *Science*, 1991, 254, 1326.
3. Wise, K.D.; Najafi, K. *Science*, 1991, 254, 1335.
4. Aspnes, D.E. *Thin Solid Films*, 1982, 89, 249.
5. Aspnes, D.E.; Heller, A.; Porter, J.D.; *J. Appl. Phys.*, 1986, 60, 3028.
6. Jin, S.; Tiefel, T.H.; Wolfe, R.; Sherwood, R.C.; Mottine, J.J., Jr. *Science*, 1992, 255, 446.
7. Heller, A.; Aspnes, D.E.; Porter, J.D.; Sheng, T.T.; Vadimsky, R.G. *J. Phys. Chem.*, 1985, 89, 4444.
8. Tierney, M.J.; Martin, C.R. *J. Phys. Chem.*, 1989, 93, 2878.
9. Foss, C.A., Jr.; Hornyak, G.L.; Stockert, J.A.; Martin, C.R. (manuscript in preparation).
10. Despic, A.; Parhutik, V. in Bockris, J. O'M.; White, R.E.; Conway, B.E. (Eds.), *Modern Aspects of Electrochemistry*, Plenum Press New York, 1989, Chapter 6.
11. Andersson, A.; Hunderi, O.; Granqvist, C.G. *J. Appl. Phys.*, 1980, 51, 754.
12. Lynch, D.W.; Hunter, W.R. in Palik, E., (Ed.), *"Handbook of Optical Constants of Solids"*, Academic Press, New York, 1985, p. 294.
13. Cai, Z.; Martin, C.R. *J. Am. Chem. Soc.* 1989, 111, 4138.


Figure Captions:

Figure 1. A) Transmission electron micrograph of porous alumina membrane prepared in 2% oxalic acid at 40 V. Scale bar = 50 nm. B) Transmission electron micrograph of a cross-section of an alumina membrane after deposition of the Au nanocylinders. The cylinders are dispersed in a layer ca. 1 μm from the top face of the membrane (top of micrograph) Arrow points to nanocylinder layer. Scale bar = 1 μm .

Figure 2. Transmission spectrum of alumina membrane before deposition of Au particles (Curve A) and Au/alumina composite membrane containing sphere-like Au particles 50 nm in diameter (Curve B).

Figure 3. Absorption spectrum of Au/alumina composite membranes. Curve A: particle diameter = 50 nm, particle length = 50 nm. Curve B: particle diameter = 50 nm, particle length = 300 nm.

Figure 4. Simulated absorption spectra based on equation 1 and Au optical properties from reference 7. Curve A: $K = 2$, $f_m = 0.05$, path length = 0.3 μm . Curve B: $K = 1.2$, $f_m = 0.15$, path length = 0.48 μm .

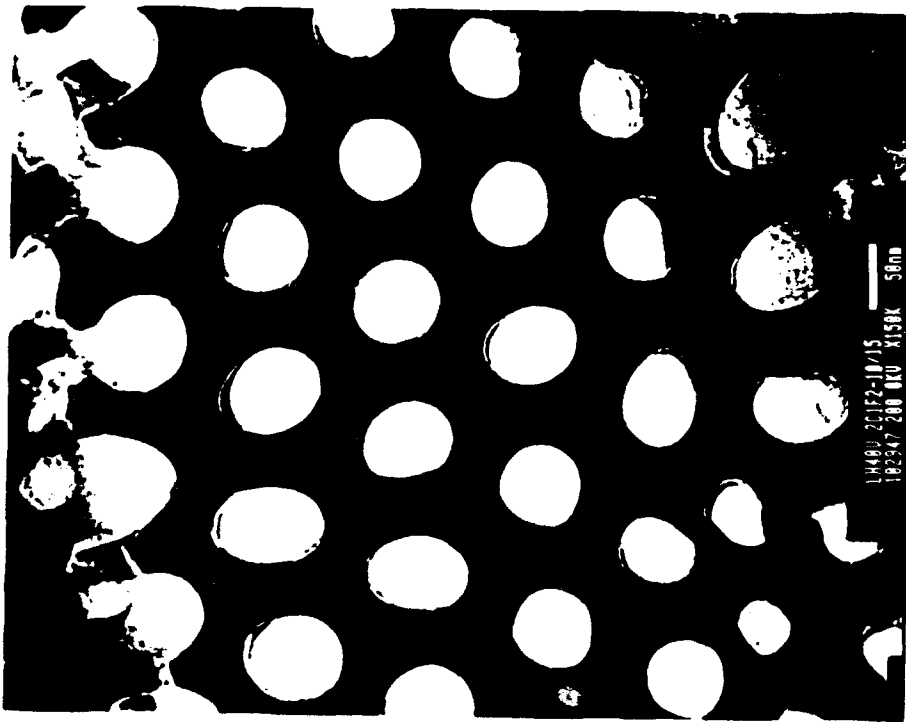

A



B

