


AD-A264 076



ARL-TR-13

AR-007-133



DEPARTMENT OF DEFENCE
DEFENCE SCIENCE AND TECHNOLOGY ORGANISATION
AERONAUTICAL RESEARCH LABORATORY

MELBOURNE, VICTORIA

Technical Report 13

DTIC
ELECTE
MAY 13 1993
S c D

ENVIRONMENTAL CORROSIVITY AT OAKLEY ARMY AIR BASE, QLD.
AUGUST 1991 TO AUGUST 1992

by

P.W. HABERECHT
B.R.W. HINTON

Approved for public release.

© COMMONWEALTH OF AUSTRALIA 1993

FEBRUARY 1993

93 5 1 00 5

93-10329
|||||

This work is copyright. Apart from any fair dealing for the purpose of study, research, criticism or review, as permitted under the Copyright Act, no part may be reproduced by any process without written permission. Copyright is the responsibility of the Director Publishing and Marketing, AGPS. Enquiries should be directed to the Manager, AGPS Press, Australian Government Publishing Service, GPO Box 84, CANBERRA ACT 2601.

**DEPARTMENT OF DEFENCE
DEFENCE SCIENCE AND TECHNOLOGY ORGANISATION
AERONAUTICAL RESEARCH LABORATORY**

Technical Report 13

**ENVIRONMENTAL CORROSIVITY AT OAKLEY ARMY AIR BASE, QLD.
AUGUST 1991 TO AUGUST 1992**

by

**P.W. HABERECHT
B.R.W. HINTON**

SUMMARY

The BELL 206-B1 helicopters at Oakley Army Air Base are often placed in storage hangars, for periods of 90 days or more. The OEM recommends the aircraft should be stored in a special plastic protective bag and a dehumidifier attached to the protective bag. The use of this protection may not be warranted since the measured rate of corrosion in the storage facilities, using the CLIMAT or wire on bolt assessment method, indicates that the corrosion rate is 'negligible' for the assessed 12 month period. Additional to this evaluation, testing of Water Displacing Corrosion Preventatives (WDCP's) was carried out. The results clearly show that at the exposed Oakley sites, the WDCP's provided very good protection.



© COMMONWEALTH OF AUSTRALIA 1993

POSTAL ADDRESS: Director, Aeronautical Research Laboratory
506 Lorimer Street, Fishermens Bend 3207
Victoria Australia

TABLE OF CONTENTS

1.	INTRODUCTION	1
2.	EXPERIMENTAL DETAIL	1
2.1	Weather Monitoring.....	2
3.	RESULTS	2
3.1	Corrosion Indices - August 91 to August 92	2
3.2	Water Displacing Corrosion Preventatives (WDCP's)	3
3.3	Local Climate and Environmental Corrosivity	3
4.	CONCLUSIONS.....	4
5.	REFERENCES	5

TABLE 1

FIGURES 1-6

DISTRIBUTION

DOCUMENT CONTROL DATA

Approved For Release AUTHORITY DATE BY COMMENTS	
By _____ Distribution/	
Availability Codes	
Dist	Avail. and/or Special
A-1	

END 1

1. INTRODUCTION

To prevent corrosion during the storage of Bell 206-B1 helicopters for periods greater than 90 days, the aircraft are enclosed in a Global Redicover Bag (Figure 1), which is connected to a dehumidifier (1). Although these one-piece bags with a special airtight maxigrip zipper are fabricated from a tough, abrasion resistant polyurethane film, they are susceptible to punctures, tears and failure (2)(3). They are not readily available at the Oakey Army Air Base, and their replacement cost is approximately \$20,000.

To confirm the need or otherwise, for their use, an assessment of the corrosion severity of the local environment at the Oakey Army Air Base was instigated at the request of both RAAF and Army.(4) The corrosivity of the atmospheric environment over twelve months was determined at the following locations:

- (1) a storage hangar,
- (2) an exposed area outside a storage area,
- (3) an exposed site in the vicinity of aircraft ground operations.

This report summarises the seasonal corrosivity patterns for the twelve months from August 1991 to August 1992. An evaluation of the efficiency of a number of different water displacing corrosion preventatives (WDCPs) was also carried out.

2. EXPERIMENTAL DETAIL

The technique used to determine atmospheric corrosivity employs a CLIMAT Specimen (CLassify Industrial and Marine Atmospheres) (5). This specimen consists of 90 cm of aluminium wire (0.875 mm diameter) wound tightly into the threads of a coarsely threaded bolt (12 mm diameter, 1.5 mm pitch).

The bolts are made from steel, copper or a non-metal such as nylon, teflon etc. When exposed to the environment, galvanic corrosion and crevice corrosion occur between the aluminium/copper (Al/Cu) or aluminium/steel (Al/Fe) bimetallic couples. Only crevice corrosion occurs on the Al/Nylon specimen. The advantages of the specimen design are:

- (1) the wire provides a large surface area for corrosion, which minimises errors in determining the corrosion rate, and
- (2) various rates of corrosion relating to the classification of a particular environment can be obtained by the choice of a suitable metal bolt.

The rate of corrosion is determined by calculating the weight-loss for the aluminium wire over a given exposure period, usually 90 days. A 'Corrosivity Index' for each bimetallic couple is then calculated as follows:

$$\text{CLIMAT Indices} = \frac{\% \text{ weight loss}}{\text{Days exposure}} \times 90$$

$$\% \text{ weight loss} = \frac{\text{weight loss} + \text{losses due to chemical cleaning}}{\text{initial weight}} \times 100$$

These indices are widely used to classify the severity of atmospheric environments. Extensive research (5-11) has shown that the Al/Cu specimen has a higher rate of corrosion than the Al/Fe specimen in industrial atmospheres, while in marine environments the Al/Fe specimen has a higher rate of corrosion than the Al/Cu specimen. Thus, the Al/Cu specimens are generally used to classify industrial atmospheres and the Al/Fe specimens to classify marine environments.

Duplicate Al/Cu, Al/Fe, Al/Nylon CLIMAT specimens were prepared and mounted on six racks. The specimens on one rack were coated with water-displacing corrosion preventative's (WDCPs) WD40, Boeshield T9, and Amlguard MIL-C-85054. WDCPs have been used successfully to temporarily prevent corrosion on aircraft structure, and ARL has commenced a program to determine their effectiveness in preventing corrosion on land-based structures. The current project provided an opportunity to extend this program.

The location of specimen racks, installed at the Oakey Base (12-15), are listed in Table 1. The rack containing specimens coated with the WDCPs was installed at the control tower.

In order to determine the corrosivity at the Base over a full year, a total of 4 set. of specimens were installed at 90 day intervals, commencing on the 22nd August 1991 and concluding on the 24th August 1992. The accumulated results provide an indication of seasonal climatic variations compared to the measured corrosivity of the environment.

2.1 Weather Monitoring

Monthly weather data for Rainfall (mm), Max Temp (°C) and Relative Humidity (%) at 9 am were obtained from the Bureau of Meteorology, Oakey Aero. Met. Office (16,17) for the period of January 1991 to September 1992, which includes the 12 month period of investigation.

3. RESULTS

3.1 Corrosion Indices - August 91 to August 92

Figures 2 and 3 compare the 'Corrosion Indices' obtained with Al/Cu or Al/Fe couples after exposure over the 12 month period. It should be noted that scatter in the CLIMAT results for the Al/Cu and Al/Fe couples (12-15) is ± 0.1 index points. This data indicates that over four successive seasons, the outside environment (ie Control tower) is more corrosive than the indoor environment (ie Long term storage hangar). The range of results for the outside specimens were index values of 0.5 to 2.10 (Al/Cu couple) and 0.3 to 2.60 (Al/Fe couple). Figures 4 and 5 show specimens after exposure on the control tower and in the long term storage hangar.

Based on these values, general environmental corrosivity of the Oakey Aviation Area, was found to be in a range of index values of 0.5 to 2.6 (Al/Fe couple) and 0.3 to 2.1 (Al/Cu couple). The CLIMAT assessment may thus be classified as negligible to moderate with a brief moderate to severe condition experienced in Autumn.

The range of index values for the indoor specimens were from 0.00 to 0.10 (Al/Fe couple) and 0.00 to 0.20 (Al/Cu couple). No significant corrosion had occurred in the enclosed areas over the past 12 months of evaluation. The long term and short term storage areas had the lowest recorded corrosivity of all of the indoor specimens and the range of results were index values of 0.00 to 0.01 (Al/Fe couple) and 0.00 to 0.01 (Al/Cu couple).

These results indicate that the environmental corrosivity within the storage facilities is "Negligible". Given the very low corrosivity of the storage area, it is difficult to see that the use of the Redicover bags and dehumidifier would provide enough extra corrosion protection to justify the expense associated with their purchase and use.

3.2 Water Displacing Corrosion Preventatives (WDCP's)

Compared with the unprotected specimens exposed on the control tower, very little corrosion was detected on any of those treated with WDCP's at the end of each of the four consecutive periods.

All of the WDCP's reduced the measured corrosion rate by around 90%. These results indicate that one application of any one of the WDCP's will effectively inhibit corrosion in this environment for a period of at least 3 months. Subject to Original Equipment Manufacturer (OEM's) approval, the recommended WDCP's could be considered as a temporary corrosion protection method for metallic components during storage.

Caution should be exercised in only using the OEM's recommended MILSPEC WDCP's, with special attention to type of WDCP's and to the areas of permitted application.

The three WDCP's used for the experiment were WD40 (Oily film), Boeshield (Waxy film), Amlguard (Hard film). After 90 days exposure, the oily and waxy film specimens were found to be lightly coated with dust particles adhering to the WDCP coating.

3.3 Local Climate and Environmental Corrosivity

In figure 6 environmental corrosivity ('CLIMAT index' from the Al/Fe couple) and the climatic variables are plotted for each month over the past year.

There is no obvious correlation between the averaged monthly climatic variables (figure 6) and the seasonal variations in environmental corrosivity. The higher rainfall during summer did not apparently increase the corrosivity of the environment.

The higher environmental corrosivity measured during Autumn could be related to other non-climatic factors such as: airborne contaminants, arising from the local use of fertilisers, used during the preparation for planting of the local grain crops or, the aerial spraying of herbicides and pesticides.

It is important to understand that if the stored components were to have been coated with salt or other contaminants, as a result of coastal operations, and were not washed prior to storage, then the rate of corrosion experienced by these components would be dramatically affected, independent of the general environment that exists within the storage facilities.

4. CONCLUSIONS

- (a) The corrosivity of the outdoor environment, during the season of Autumn, was significantly greater than for the other seasons.
- (b) On the basis of the 12 month test period, the environments in the long term storage hangar and the short term storage hangar are classified as having "Negligible" ⁽⁵⁾ corrosivity.
- (c) The dehumidification of the storage facilities⁽¹⁾ for the Bell 206B-B1 Helicopters, and the use of the Redicover bags, would not provide enough extra corrosion protection, given the low corrosivity index for the storage facility, to justify their use.
- (d) One application of any one of the WDCP's tested effectively inhibited corrosion for a 3 month period.

5. REFERENCES

- (1) RAAF - AAP7210.010-2-1 AL19
Para 943b Storage procedure
- (2) RAAF - AAP7210.010-2-1 AL12
/9C-3 Para 5b Storage procedure
- (3) RAAF - AAP7210.010-2-1 AL12
/9C-7 Para 8 Storage procedure
- (4) RAAF - HQLC Minute: AIR2/4080/A17/26 Pt 1 (7) - 4th July 1991.
Determination of Corrosive Levels at Oakey Air Base QLD.
- (5) Doyle, D.P., and Wright, T.E.
Rapid method for determining atmospheric corrosivity and corrosion resistance.
Ed. W.H. Ailor; The Electrochemical Society Inc. New Jersey, 1982, 227-243.
- (6) Doyle, D.P., and Wright, T.E.
Quantitative assessment of atmospheric corrosion. Galvanic Corrosion ASTM STP978, Ed. H.P. Hack, 1988, 161-173.
- (7) Doyle, D.P., and Godard H.P.
A rapid method for determining the corrosivity of the atmosphere at any location.
Nature, 4912, 1963, 1167-1168.
- (8) Compton, K.G., Mendizza, A. and Bradley, W.W.
Atmospheric galvanic couple corrosion. Corrosion, 11, 9, 1955, 35-44.
- (9) Doyle, D.P., and Godard H.P.
Rapid determination of corrosivity of an atmosphere to aluminium. Proc. 3rd Int. Cong. on Metallic Corrosion, MIR Publishers, Moscow, USSR, 4, 1969, 429-437
- (10) Hsien, C.C. and Lin, C.C. (1987)
Atmospheric corrosivity survey in Taiwan R.O.C.. 5th Asian-Pacific Corrosion Control Conf., 2, 1987, 1-5.
- (11) King, G.A. and Gibbs, P.
A corrosivity Survey on a Grid of Sites Ranging from Rural to Moderately Severe Marine Part 2 - ATCORR Indices. Corrosion Australasia, 15, 1, 1988.
- (12) Haberecht, P.W. and Hinton, B.R.W.
Environmental Corrosivity at Oakey Army Air Base, Qld. September to November 1991 - Interim Report ARL Letter Report No. 1/92
- (13) Haberecht, P.W. and Hinton, B.R.W.
Environmental Corrosivity at Oakey Army Air Base, Qld. November 1991 to February 1992 - Interim Report ARL Letter Report No. 2/92

-
- (14) Haberecht, P.W. and Hinton, B.R.W.
Environmental Corrosivity at Oakey Army Air Base, Qld. March 1992 to June 1992 - Interim Report ARL Letter Report No. 3/92
- (15) Haberecht, P.W. and Hinton, B.R.W.
Environmental Corrosivity at Oakey Army Air Base, Qld. - Final Report ARL Letter Report No. 4/92
- (16) Bureau of Meteorology - Dept of Science Data
*Monthly Summary Statistics Year 1991 - Oakey Aero Met Office - Oakey Army Airbase, Oakey Qld. Station 041359.
Lat 27 25 S, Lng 151 44 E Elevation 406.4m*
- (17) Bureau of Meteorology - Dept of Science Data
*Monthly Summary Statistics Jan-Nov 1992 - Oakey Aero Met Office - Oakey Army Airbase, Oakey Qld. Station 041359.
Lat 27 25 S, Lng 151 44 E Elevation 406.4m*

ACKNOWLEDGMENT

The authors wish to thank the following people for their assistance with this work:

WO. E.Klein,
WO. J. Ottoborino,
WO. P.Napier,
Lt. S.Evans

Table 1:

Locations of CLIMAT specimens at Oakey Base

1	Long term storage hangar for Bell 206B Helicopters and Pilatus Porter Aircraft.
2	Aviation support workshop.
3	Short / Long term storage hangar for Blackhawk Helicopter and Pilatus Porter Aircraft.
4	Major daily storage and maintenance area for operational aircraft.
5	General operations e.g. start up and taxi-ing area for helicopters.
6	Control Tower (Northerly aspect).

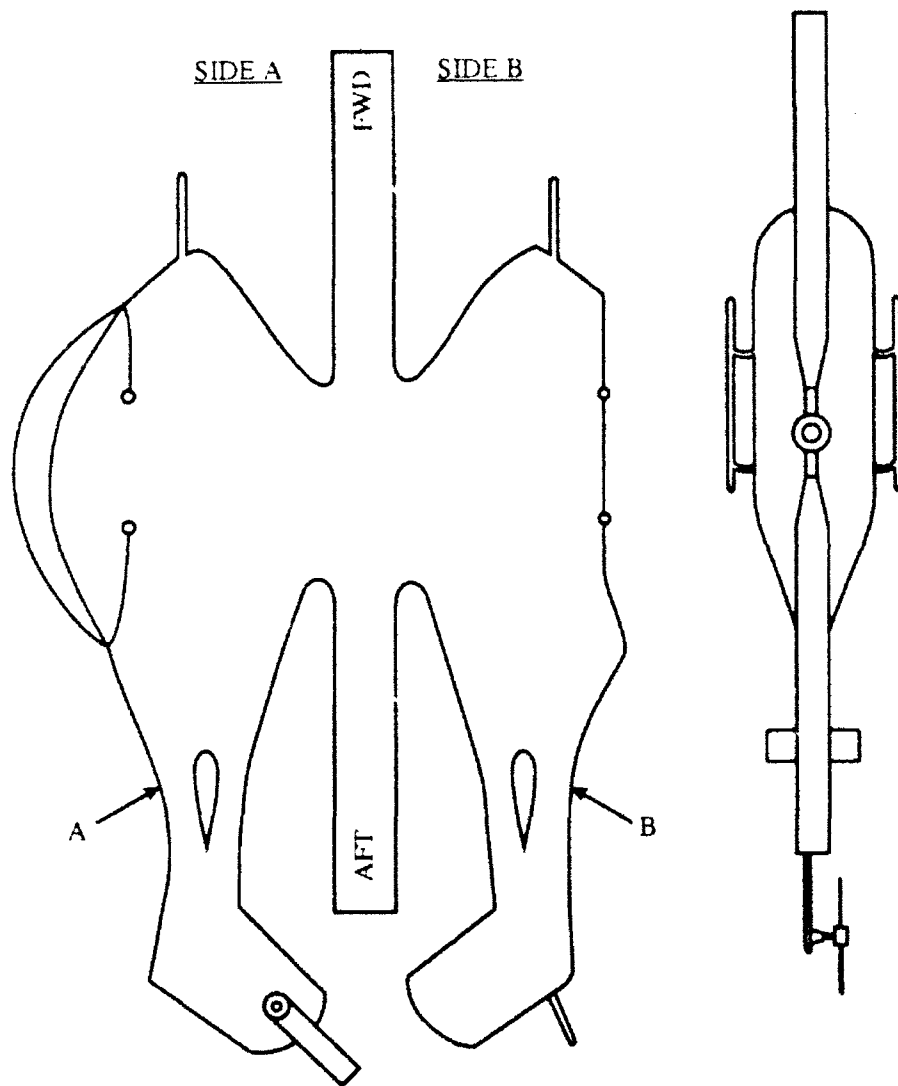


Figure 1: The Global Redicover Bag for Long term Storage of the Bell 206-B1 Helicopter

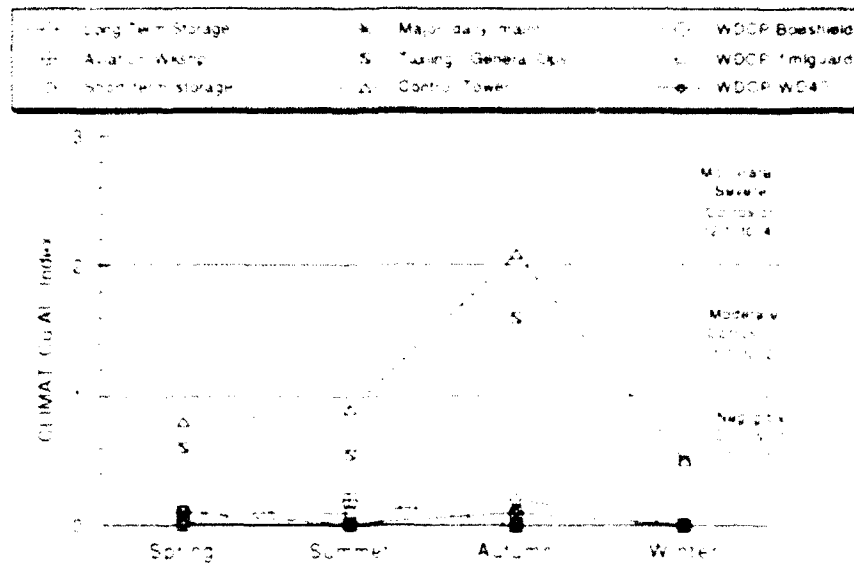


Figure 2: CLIMAT Corrosion indices obtained with the Al/Cu couple at various Base locations from Aug 91 to Aug 92.



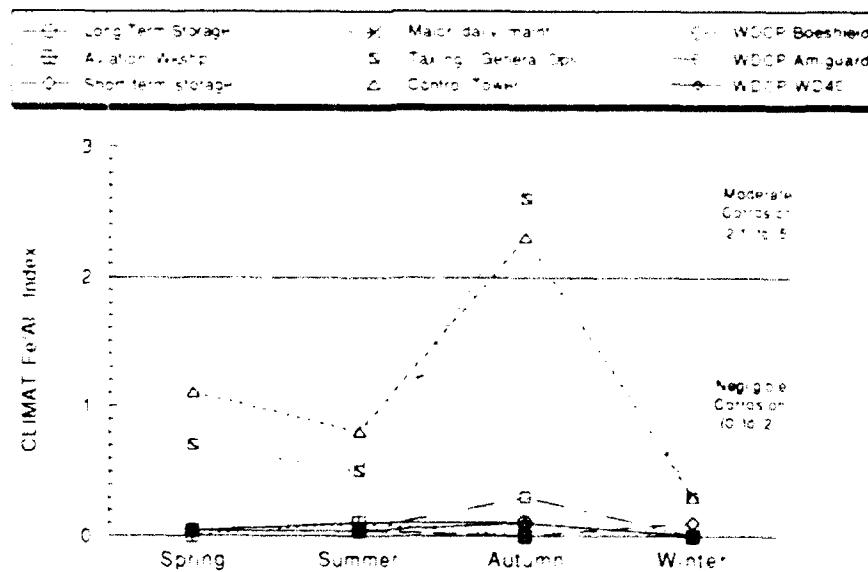


Figure 3: CLIMAT Corrosion indices obtained with the Al/Fe couple at various Base locations from Aug 91 to Aug 92.

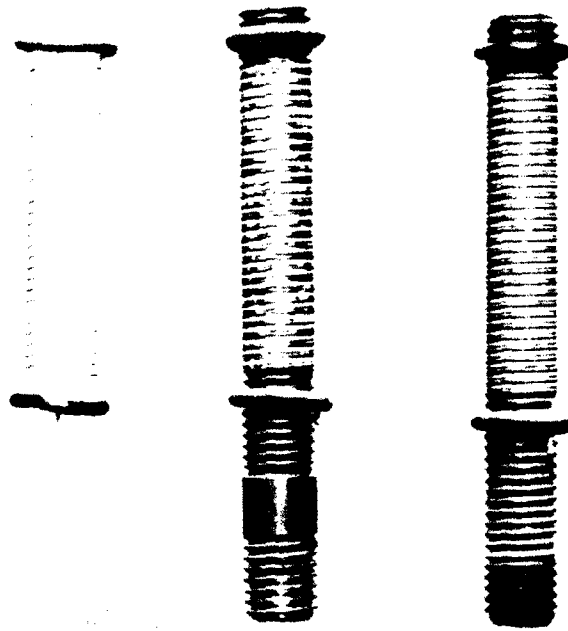

June 92 Aug 92: Control Tower

Figure 4: CLIMAT Specimens after 90 days exposure on the control tower northern balcony at Oakey.

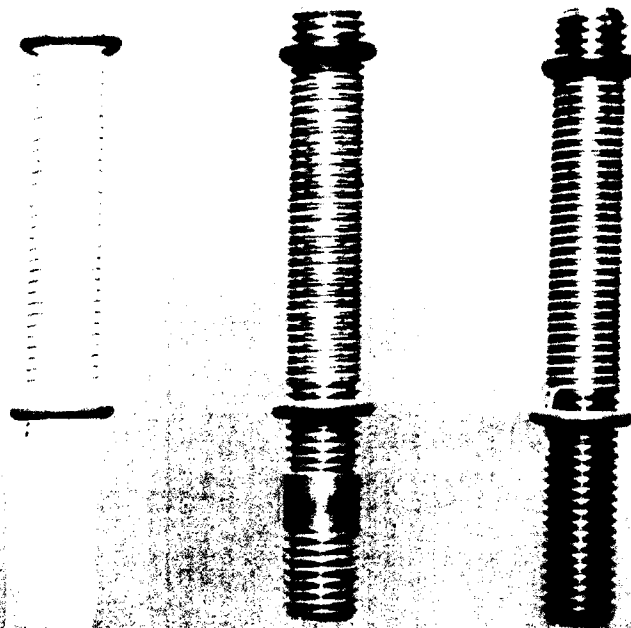

Long Term
Storage Hangar

Figure 5: CLIMAT Specimens after 90 days exposure in the long term storage hangar at Oakey.

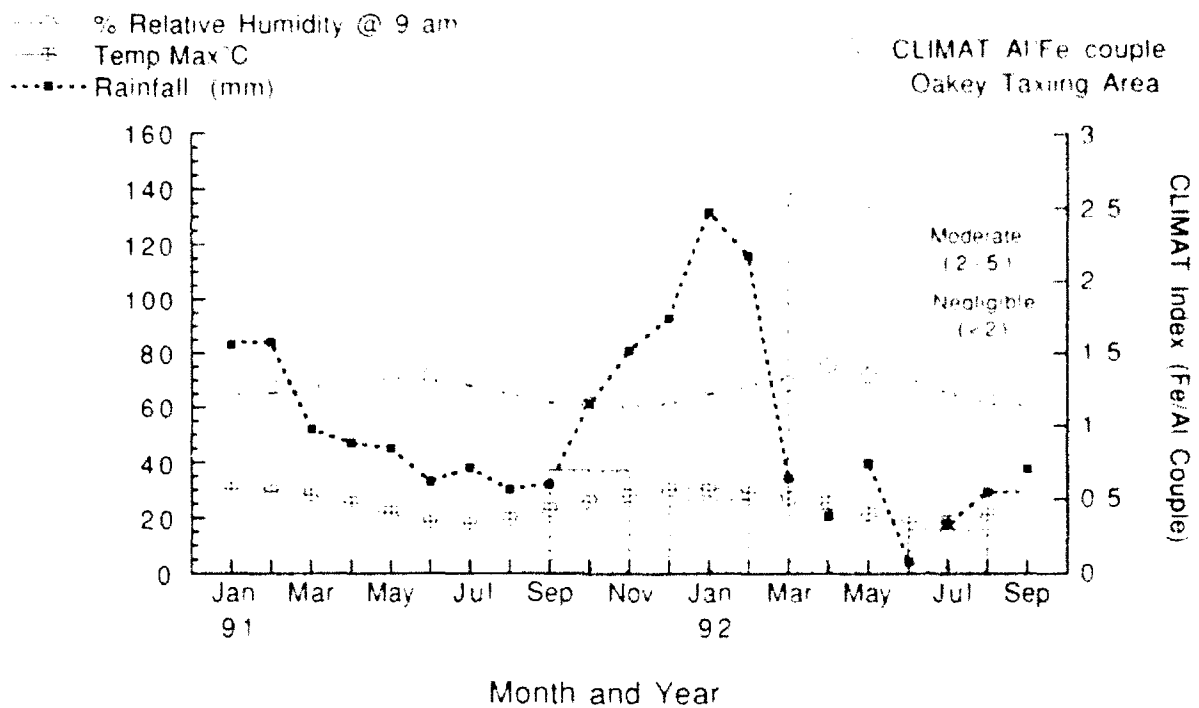


Figure 6: CLIMAT Corrosion indices obtained with the Al/Fe couple compared to measured climatic conditions for 12 months.

DISTRIBUTION

AUSTRALIA

Department of Defence

Defence Central

Chief Defence Scientist	}	shared copy
AS, Science Corporate Management		
FAS Science Policy		
Director, Departmental Publications		
Counsellor, Defence Science, London (Doc Data sheet only)		
Counsellor, Defence Science, Washington (Doc Data sheet only)		
Scientific Adviser, Defence Central		
OIC TRS, Defence Central Library		
Document Exchange Centre, DSTIC (8 copies)		
Defence Intelligence Organisation		
Librarian H Block, Victoria Barracks, Melb (Doc Data sheet only)		

Aeronautical Research Laboratory

Director
Library
Chief, Airframes and Engines Division
Authors: P.W. Haberecht
B.R.W. Hinton

Navy Office

Navy Scientific Adviser (3 copies Doc Data sheet only)

Army Office

Scientific Adviser - Army (Doc Data sheet only)

Air Force Office

Air Force Scientific Adviser
OIC CAME
OIC ATF, ATS, RAAFSTT, WAGGA (2 copies)

Universities and Colleges

RMIT
Library

SPARES (5 COPIES)

TOTAL (28 COPIES)

DOCUMENT CONTROL DATA

PAGE CLASSIFICATION
UNCLASSIFIED

PRIVACY MARKING

1. AR NUMBER AR-007-133	10. ESTABLISHMENT NUMBER ARL-TR-13	2. DOCUMENT DATE FEBRUARY 1993	3. TASK NUMBER AIR 90/037
4. TITLE ENVIRONMENTAL CORROSIVITY AT OAKEY ARMY AIR BASE, QLD AUGUST 1991 TO AUGUST 1992		5. SECURITY CLASSIFICATION (PLACE APPROPRIATE CLASSIFICATION IN BOXES: (S) SECRET (C) CONFIDENTIAL RESTRICTED (R) UNCLASSIFIED (U)) U U U DOCUMENT TITLE ABSTRACT	6. NO. PAGES 13 7. NO. REFS 17
8. AUTHOR(S) P.W. HABERECHT B.R.W. HINTON		9. DOWNGRADING/DELIMITING INSTRUCTIONS Not applicable	
10. CORPORATE AUTHOR AND ADDRESS AERONAUTICAL RESEARCH LABORATORY AIRFRAMES AND ENGINES DIVISION 506 LORIMER STREET FISHERMENS BEND VIC 3207		11. OFFICE/POSITION RESPONSIBLE FOR: SPONSOR RAAF SECURITY DOWNGRADING APPROVAL CAED	
12. SECONDARY DISTRIBUTION OF THIS DOCUMENT Approved for public release. OVERSEAS ENQUIRIES OUTSIDE STATED LIMITATIONS SHOULD BE REFERRED THROUGH DSTIC ADMINISTRATIVE SERVICES BRANCH, DEPARTMENT OF DEFENCE, ANZAC PARK WEST OFFICES, ACT 2601.			
13a. THIS DOCUMENT MAY BE ANNOUNCED IN CATALOGUES AND AWARENESS SERVICES AVAILABLE TO: No limitations.			
13b. CITATION FOR OTHER PURPOSES (E.G. CASUAL ANNOUNCEMENT) MAY BE X UNRESTRICTED OR AS FOR 13a.			
14. DESCRIPTORS Army Aviation Centre Atmospheric corrosion BELL 206-B1 helicopters Corrosion environments Corrosion inhibitors			15. DISCAT SUBJECT CATEGORIES 0102 010301 110601
16. ABSTRACT <i>The BELL 206-B1 helicopters at Oakey Army Air Base are often placed in storage hangars, for periods of 90 days or more. The OEM recommends the aircraft should be stored in a special plastic protective bag and a dehumidifier attached to the protective bag. The use of this protection may not be warranted since the measured rate of corrosion in the storage facilities, using the CLIMAT or wire on bolt assessment method, indicates that the corrosion rate is 'negligible' for the assessed 12 month period. Additional to this evaluation, testing of Water Displacing Corrosion Preventatives (WDCP's) was carried out. The results clearly show that at the exposed Oakey sites, the WDCP's provided very good protection.</i>			

PAGE CLASSIFICATION
UNCLASSIFIED
PRIVACY MARKING

THIS PAGE IS TO BE USED TO RECORD INFORMATION WHICH IS REQUESTED BY THE ESTABLISHMENT FOR ITS OWN USE BUT WHICH WILL NOT BE ADDED TO THE DISIS DATA UNLESS SPECIFICALLY REQUESTED

16. ABSTRACT CONT

17. IMPRINT

AERONAUTICAL RESEARCH LABORATORY, MELBOURNE

18. DOCUMENT SERIES AND NUMBER

Technical Report 13

19. WA NUMBER

33 322F

20. TYPE OF REPORT AND PERIOD COVERED

21. COMPUTER PROGRAMS USED

22. ESTABLISHMENT FILE REF(S)

B2/03/86

23. ADDITIONAL INFORMATION AS REQUIRED