

AD-A281 174

MENTATION PAGE

Form Approved
OMB No. 0704-0188

is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

REPORT DATE
6/28/943. REPORT TYPE AND DATES COVERED
Technical Report4. TITLE AND SUBTITLE
Synthesis of Low Band Gap Zwitterionic
and Planar Conjugated Pyrrole-Derived Polymers.
Reversible Optical Absorbances From the UV to the Near-IR5. FUNDING NUMBERS
G- N00014-89-J3062
R&T 3132084
K. Wynne

6. AUTHOR(S)

Thorsten W. Brockmann and James M. Tour

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)
Department of Chemistry and Biochemistry
University of South Carolina
Columbia, SC 292088. PERFORMING ORGANIZATION
REPORT NUMBER

15PX 94-20863

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)
Department of the Navy
Office of Naval Research
800 North Quincy Street
Arlington, VA 22217-5000

28

11. SUPPLEMENTARY NOTES

J. Am. Chem. Soc. 1994, in press.

12a. DISTRIBUTION / AVAILABILITY STATEMENT

Reproduction in whole or in part is permitted for any
purpose of the United States Government. This document has
been approved for public release and sale; its distribution
is unlimited.DTIC
S ELECTE D
JUL 08 1994
F

13. ABSTRACT (Maximum 200 words)

Described is the synthesis of a zwitterionic pyrrole-derived polymer. The monomer (1) is formally an azomethine ylide and it was synthesized in 3 steps from pyrrole. 1 was polymerized using copper-bronze in DME. The polymer had a strong optical absorbance at 512 nm in THF and an inter-unit ionic interaction is proposed to explain this large red-shifted band. If aqueous NaOH is added to the THF solution, or a Lewis basic solvent used instead of THF/NaOH, then a tremendous bathochromic shift occurs to 881 or 901 nm, respectively. The large shifts are attributed to a dramatic structural change in the polymer induced by hydroxide or Lewis base attack on the iminium unit. This causes a cascade of electron shifts to form a fully conjugated polymer that is fixed into a planar conformation. The planarization process is reversible so that addition of acid or shifting to a weaker Lewis basic solvent causes the polymer to recover its zwitterionic form and its original optical absorption characteristics. Moreover, upon mild reduction of the zwitterionic polymer with Pd/C and H₂ (1 atm), some of the extended conjugation is lost but a polymer forms that has an enormous optical absorption maximum range from the near-UV to the near-IR ($\lambda_{\max} = 886$ nm) depending on the solvent or hydroxide concentration. Further, a sample of the reduced polymer can be dispersed in platicized poly(vinyl chloride). The flexible polymer composite reversibly changed from dark blue-brown in aqueous hydroxide to bright yellow-orange in aqueous HCl.

14. SUBJECT TERMS

DTIC QUALITY INSPECTED 8

15. NUMBER OF PAGES

16. PRICE CODE

17. SECURITY CLASSIFICATION
OF REPORT
Unclassified18. SECURITY CLASSIFICATION
OF THIS PAGE
Unclassified19. SECURITY CLASSIFICATION
OF ABSTRACT
Unclassified20. LIMITATION OF ABSTRACT
UL

94 7 7 091

OFFICE OF NAVAL RESEARCH

GRANT : N00014-89-J-3062

R&T Code 3132084

Technical Report No. 28

Synthesis of Low Band Gap Zwitterionic and Planar Conjugated Pyrrole-Derived Polymers.
Reversible Optical Absorbances From the UV to the Near-IR

by

Thorsten W. Brockmann and James M. Tour

Accepted for Publication in

Journal of the American Chemical Society

Department of Chemistry and Biochemistry
University of South Carolina
Columbia, SC 29208

June 28, 1994

Reproduction in whole, or in part, is permitted for any purpose of the United States Government

This document has been approved for public release and sale; its distribution is unlimited.

Accession For		
NTIS	CRA&I	☒
DTIC	TAB	☐
Unannounced		☐
Justification		
By		
Distribution /		
Availability Codes		
Dist	Avail and/or Special	
A-1		

JA940746V, Revised

Synthesis of Low Band Gap Zwitterionic and Planar Conjugated Pyrrole-Derived Polymers. Reversible Optical Absorptions From the UV to the Near-IR

Thorsten W. Brockmann and James M. Tour*

Department of Chemistry and Biochemistry

University of South Carolina

Columbia, South Carolina 29208


Abstract

Described is the synthesis of a zwitterionic pyrrole-derived polymer. The monomer (1) is formally an azomethine ylide and it was synthesized in 3 steps from pyrrole. 1 was polymerized using copper-bronze in DME. The polymer had a strong optical absorbance at 512 nm in THF and an inter-unit ionic interaction is proposed to explain this large red-shifted band. If aqueous NaOH is added to the THF solution, or a Lewis basic solvent used instead of THF/NaOH, then a tremendous bathochromic shift occurs to 881 or 901 nm, respectively. The large shifts are attributed to a dramatic structural change in the polymer induced by hydroxide or Lewis base attack on the iminium unit. This causes a cascade of electron shifts to form a fully conjugated polymer that is fixed into a planar conformation. The planarization process is reversible so that addition of acid or shifting to a weaker Lewis basic solvent causes the polymer to recover its zwitterionic form and its original optical absorption characteristics. Moreover, upon mild reduction of the zwitterionic polymer with Pd/C and H₂ (1 atm), some of the extended conjugation is lost but a polymer forms that has an enormous optical absorption maximum range from the near-UV to the near-IR ($\lambda_{\text{max}} = 886 \text{ nm}$) depending on the solvent or hydroxide concentration. Further, a sample of the reduced polymer can be dispersed in plasticized poly(vinyl chloride). The flexible polymer composite reversibly changed from dark blue-brown in aqueous hydroxide to bright yellow-orange in aqueous HCl.

In an effort to maximize the extended π -conjugation in polymers and to study their corresponding electronic and optical properties, several have undertaken the synthesis of new conjugated organic polymers that have a planar or near-planar conformation between the consecutive repeat units.^{1,2} Described here is the synthesis of a unique zwitterionic pyrrole-derived polymer that can reversibly convert to a linear and planar conjugated polymer with a solution band gap of approximately 1.1 eV. The material possesses a reversible and enormous pH-dependent or solvent dependent absorption spectral range from the UV to the near-IR spectral region. Soluble polymeric materials that can respond dramatically and reversibly to external stimuli could have importance in the development of organic-based optical and electronic sensors,² while polymers with absorbances in the near-IR can serve as dyes for optical data discs.³

The synthesis of the new pyrrole-derived zwitterionic polymer is described in Scheme 1.

Scheme 1

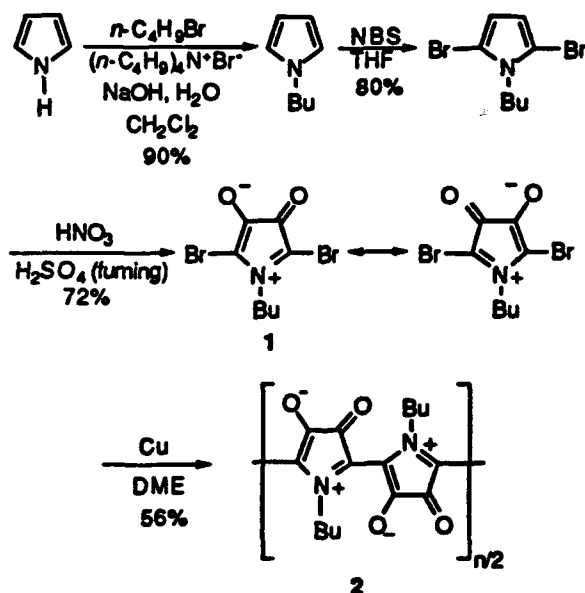

Pyrrole was N-alkylated under standard phase transfer conditions.⁴ Bromination⁵ and vigorous oxidation yielded the zwitterionic monomer 1, a carbonyl-stabilized azomethine ylide, in an overall 52% yield for the three steps. The FTIR (KBr, 1718 cm^{-1} , with no hydroxyl absorbance), mass spectrum (calc'd for $\text{C}_8\text{H}_9\text{Br}_2\text{NO}_2$: 311; found: 311), elemental analysis (calc'd: C, 30.89; H,

2.92; Br, 51.39; N, 4.50; found: C, 30.90; H, 2.92; Br, 51.25; N, 4.48), UV spectrum (CH_2Cl_2 , $\lambda = 248, 322$; NMP, $\lambda = 281, 320$ (sh); there was little change in the UV spectra in the presence of aqueous NaOH or aqueous HCl), ^1H NMR [(300 MHz, CDCl_3) δ 3.59 (t, $J = 7.3$ Hz, 2 H), 1.57 (p, $J = 7.1$ Hz, 2 H), 1.30 (sext, $J = 7.3$ Hz, 2 H), 0.91 (t, $J = 7.3$ Hz, 3 H)] and ^{13}C NMR [(75 MHz, CDCl_3) δ 163.85, 129.24, 39.48, 30.39, 19.82, 13.52] were all consistent with the proposed structure. Note that two resonance forms exist for **1**, therefore there are only six peaks in the ^{13}C NMR spectrum.


We then sought to polymerize **1** using a variety of coupling methods.⁶ $(\text{COD})_2\text{Ni}(0)$,⁷ copper(II) triflate,⁸ and Rieke copper⁹ failed to afford any polymeric product. Classical Ullman¹⁰ coupling using copper-bronze (Aldrich) also failed when utilizing the common solvents (DMF, quinoline, tetramethylurea, or pyridine), however, in DME, copper-bronze-promoted polymerization (200°C, screw cap tube, 18 h) of **1** afforded the desired polymer **2** (Scheme 1) in 56% yield after fractional precipitation (CH_2Cl_2 , CH_3OH). The precipitation dramatically sharpened the polydispersity (PD) to 1.15-1.25 with $M_n = 3,910$ (SEC, PS standards).¹¹ If the reaction was run for 40 h, the molecular weight peaked at $M_n = 4,980$ with PD = 1.54. Continued heating caused no increase in the molecular weight. Spectral analysis again confirmed the proposed structure: FTIR (film, 1697 cm^{-1} , with no hydroxyl absorbance), elemental analysis (calc'd for $\text{C}_8\text{H}_9\text{NO}_2$: C, 63.56; H, 6.00; N, 9.26; found: C, 63.40; H, 6.71; Br, <0.5; Cu, <0.02; N, 8.06), ^1H NMR [(300 MHz, CDCl_3) δ 3.40 (br s, 2 H), 1.55 (br s, 2 H), 1.27 (br s, 2 H), 0.89 (br t, $J = 7$ Hz, 3 H)], and ^{13}C NMR [(125 MHz, CDCl_3) δ 169.16, 131.07, 39.26, 30.58, 20.08, 13.92]. No detectable bromide content was observed since the excess Cu(0) carries out oxidative additions on nearly all aryl bromide locations with subsequent end group protonations on workup; a commonly observed feature of Ullman reactions.^{10b} A macrocyclic structure can not be ruled out, however, to have a pyrrole ring system with all the nitrogen atoms pointing inward would require 10 pyrrole units to complete the ring.^{6c} A macrocycle with all the oxygen atoms pointing inward would require even far more pyrrole units, therefore excluding a monomeric Cu-templation driven macrocyclization.

Compound 2 is an intrinsic semiconductor exhibiting an undoped conductivity of $1.4 \times 10^{-5} \Omega^{-1} \text{ cm}^{-1}$ and an iodine doped conductivity of $4.2 \times 10^{-4} \Omega^{-1} \text{ cm}^{-1}$ (4-point probe, pellet). The low doped conductivity of the system may be due to the presence of the carbonyl functionality which can retard polaronic or bipolaronic migrations.^{1j} Thermogravimetric analysis (TGA, $10^\circ\text{C}/\text{min}$, N_2) showed 10% weight loss at 318°C and with a rapid weight decrease at 400°C .

The optical spectra for 2 are most interesting. Polypyrrole has an absorption maximum of 420 nm (solid) but it is intractable. N-alkylated polypyrroles can be soluble, however, the increased steric repulsions between the consecutive aryl units causes a hypsochromic shift to approximately 380 nm.⁶ Remarkably, the absorption maximum of 2 exhibits a strong bathochromically shifted absorbance that may be due to ionic interactions that force a diminution in the inter-unit twist angle.² Solvatochromic effects are consistent with this proposal in that the following trend of S_0 - S_1 ($\pi\pi^*$) absorption maxima are present for 2: CCl_4 , 520 nm; THF, 512 nm (Figure 1); EtOH/THF (1:1), 503 nm; acetone, 482 nm; H_2SO_4 , 498 nm (with strong hypochromicity that is indicative of a protonic substitution effect). Thus when the charges can be solvent stabilized, inter-unit stabilization/planarization is retarded and the absorption shifts hypsochromically. Likewise, stabilization of the polar ground state increases the energy gap of the π - π^* transition which may exhibit charge transfer character.^{3,12} Remarkably, when aqueous NaOH (0.05 M) was added dropwise to 2 in THF, the initial red-colored solution ($\lambda_{\text{max}} = 512$ nm) became pale-orange and then finally brown ($\lambda_{\text{max}} = 881$ nm) as more base was added (Figure 1). This pH-dependent shift in the absorption spectrum was reversible but polymer decomposition was detected after a few hours in the hydroxide-containing medium. Equally impressive solution effects occurred upon the dissolution of 2 in strongly Lewis basic solvents¹² such as HMPA ($\lambda_{\text{max}} = 901$ nm) or NMP ($\lambda_{\text{max}} = 746$ nm) (2 was insoluble in DMSO) (Figure 2).¹³ No polymer decomposition was detected in these Lewis basic solvents. Upon the addition of aqueous HCl, the HMPA and NMP solutions once again became red with no absorption bands present above 600 nm. The ^{13}C NMR spectrum of 2 in HMPA (with 10% CDCl_3 added for the lock) showed the butyl signals as well as a broad resonance from 176-163 ppm. In accord with the dramatic and

reversible optical absorbance shifts, Brønsted or Lewis bases might be promoting a cascade of π -electron migrations in **2** to afford the planar conjugated polymer **3** (Scheme 2).

Scheme 2

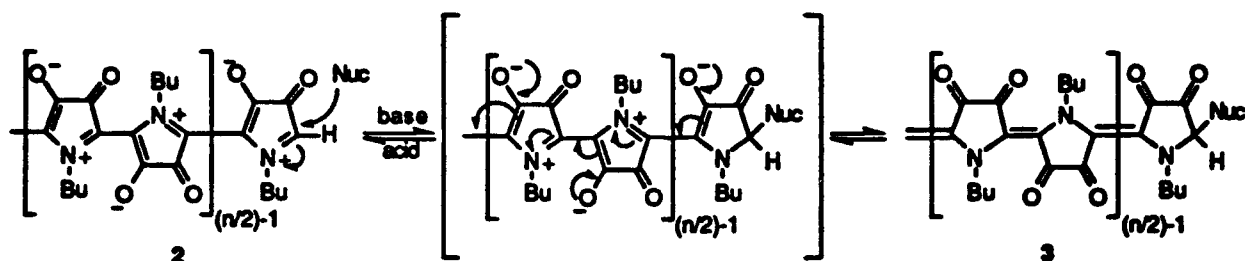

3 is similar to indigo and related indigo-like compounds that possess cross-conjugated vinylogous amides with extraordinarily large values of λ_{max} .³

We attempted to get a conductivity of **3** as the diethylamine adduct λ_{max} (Et_2NH solution) 783 nm. Removal of the excess amine and press-formation afforded pellets that were repeatedly too brittle for 4-point probe analysis. This is understandable with these extremely rigid-rod systems. Other analogs with longer alkyl chains may afford less brittle materials that are suitable for conductivity analysis.

Another interesting feature of **2** is that it could be partially reduced with H_2 (1 atm) over Pd/C (24 h, 23°C) to afford a system that is very similar to the starting polymer by FTIR, and SEC analysis, while the ^1H NMR and ^{13}C NMR showed peak broadening; therefore, some of the units were hydrogenated. Although the reduced polymer can not attain the degree of extended conjugation of **3** (as determined by the optical absorbances), its response range to different solvents can be from the UV region with weak tailing into visible, to the near-IR (DMSO, $\lambda = 886$ nm) (Figure 3). Thus the reduced polymer is soluble in DMSO and it responds most dramatically to solvent changes. When aqueous NaOH (0.05 M) was added dropwise to the reduced polymer in THF, the initial yellow-colored THF solution became green, blue-green, and finally blue as more base was added and a new absorption band appeared at 618 nm. The absorbance could be stabilized at any color along this transition depending on the amount of hydroxide added. Upon addition of aqueous HCl to the THF solution, the color moved back again over the same range before ceasing at the yellow-colored solution with a major absorption peak at < 290 nm. Unlike **3**,

the reduced polymer undergoes no noticeable hydroxide-induced decomposition upon the reversible pH shifts. Furthermore, we dissolved the reduced polymer (0.05 wgt % relative to PVC plus plasticizer) in a solution of THF, poly(vinyl chloride) (PVC), and the plasticizer di(2-ethylhexyl) phthalate (DOP). Evaporation of the THF resulted in the formation of a dark green (possibly resulting from a mixture of yellow and blue)³ transparent flexible film since DOP was acting as a Lewis base. Suspension of the film (250 μ m thickness) in aqueous HCl (3 N) (no organic solvent was present) caused the film to become bright yellow-orange while suspension in aqueous NaOH (0.5 M) caused the film to become dark blue-brown, and this process was reversible.

Acknowledgments. Support came from the Office of Naval Research, the National Science Foundation (EHR-91-08772, DMR-9158315), and industrial contributors to the NSF Presidential Young Investigator Award Program (1991-96): Hercules, IBM, Ethyl, Shell, Eli Lilly, Polaroid, Farchan, and Exxon Corporations. We thank Molecular Design Ltd. for the use of their synthetic data base, Professor Peter Chou for helpful discussions, and Dr. Yunke Zhang for help with the PVC film.

Supplementary Material Available: Detailed synthetic procedures and characterization data for the synthesis and reduction of **2** (3 pages). This material is contained in many libraries on microfiche, immediately following this article in the microfilm version of the journal, and can be ordered from the ACS; see any current masthead page for ordering information.

References and Notes

- (1) (a) Overberger, C. G.; Moore, J. A. *Adv. Polym. Sci.* 1970, 7, 113. (b) Schlüter, A.-D. *Adv. Mater.* 1991, 3, 282. (c) Yu, L.; Chen, M. Dalton, L. R. *Chem. Mater.* 1990, 2, 649. (d) Hong, S. Y.; Kertesz, M.; Lee, Y. S.; Kim, O.-K. *Chem. Mater.* 1992, 4, 378. (e) Godt, A.; Schlüter, A.-D. *Adv. Mater.* 1991, 3, 497. (f) Yu, L.; Dalton, L. R. *Macromolecules* 1990, 23, 3439. (g) Scherf, U.; Müllen, K. *Synthesis* 1992, 23. (h) Scherf, U.; Müllen, K. *Polym. Prepr. (Am. Chem. Soc., Div. Polym. Chem.)* 1994, 35(1), 200. (i) Tour, J. M.; Lamba, J. J. S. *J. Am. Chem. Soc.* 1993, 115, 4935. (j) *Handbook of Conducting Polymers*; Skotheim, T. J., Ed.; Dekker: New York, 1986.
- (2) For some recent examples of reversible conjugated polymer backbone control, see: (a) Marsella, M. J.; Swager, T. M. *J. Am. Chem. Soc.* 1993, 115, 12214. (b) McCullough, R. D.; Williams, S. P.; Jayaraman, M. *Polym. Prepr. (Am. Chem. Soc., Div. Polym. Chem.)* 1994, 35(1), 190.
- (3) Zollinger, H. *Color Chemistry*; VCH: New York, 1991.
- (4) Wang, N.; Teo, K.; Anderson, H. J. *Can. J. Chem.* 1977, 55, 4112.
- (5) Khoury, Y.; Kovacic, P.; Gilow, H. M. *J. Polym. Sci., Polym. Lett.* 1981, 19, 395.
- (6) For some background work on polypyrroles, see: (a) Street, G. B. in ref. 1j. (b) Bureau, J. M.; Gazard, M.; Champagne, M.; Dubois, J. C.; Tourillon, G.; Garnier, F. *Mol. Cryst. Liq. Cryst.* 1985, 118, 235. (c) Street, G. B.; Lindsey, S. E.; Nazzari, A. I.; Wynne, K. J. M. *Mol. Cryst. Liq. Cryst.* 1985, 118, 137.
- (7) Semmelhack, M. F.; Helquist, P. M.; Jones, L. D. *J. Am. Chem. Soc.* 1971, 93, 5908.
- (8) Cohen, T.; Cristea, I. *J. Org. Chem.* 1975, 40, 3649.
- (9) Matsumoto, H.; Inaba, I.; Rieke, R. D. *J. Org. Chem.* 1983, 48, 840.
- (10) (a) Bacon, G. R.; Stewart, O. J. *J. Chem. Soc. C* 1965, 4653. (b) Groenendaal, L.; Peerlings, H. W. I.; van Dongen, J. L. J.; Havinga, E. E.; Vekemans, J. A. J. M.; Meijer, E. W. *Polym. Prepr. (Am. Chem. Soc., Div. Polym. Chem.)* 1994, 35(1), 194.

(11) Since size exclusion chromatography (SEC) is a measure of the hydrodynamic volume and not the molecular weight (MW), significant errors in M_n and M_w may result when comparing rigid rod polymers to the flexible coils of polystyrene (PS) standards. Therefore, the values recorded here are given simply as a reference.

(12) (a) Kamlet, M. J.; Abboud, J.-L., M.; Abraham, M. H.; Taft, R. W. *J. Org. Chem.* **1983**, *48*, 2877. (b) Effenberger, F.; Würthner, F. *Angew. Chem. Int. Ed. Engl.* **1993**, *32*, 719. (c) Reichardt, C. *Angew. Chem. Int. Ed. Engl.* **1979**, *18*, 98.

(13) For some other low band gap conjugated polymers, see: (a) Wudl, F.; Kobayashi, M.; Heeger, A. J. *J. Org. Chem.* **1984**, *49*, 3382. (b) Ikenoue, Y.; Wudl, F.; Heeger, A. J. *Synth. Met.* **1991**, *40*, 1. (c) Pomerantz, M.; Chaloner-Gill, B.; Harding, L. O.; Tseng, J. J.; Pomerantz, W. J. *J. Chem. Soc., Chem. Commun.* **1992**, 1672. (d) Lambert, T. L.; Ferraris, J. P. *J. Chem. Soc., Chem. Commun.* **1991**, 752. (e) Havinga, E. E.; ten Hoeve, W.; Wynberg, H. *Polym. Bull.* **1992**, *29*, 119.

List of figures.

Figure 1. (a) Spectrum of 2 in CCl₄ (—) and THF (----) (b) Dissolution of 2 in THF/aqueous NaOH to form 3 (----).

Figure 2. Dissolution of 2 in (a) HMPA (—) and (b) NMP (----).

Figure 3. Spectrum of the reduction product of 2. (a) In THF (—) and (b) in DMSO (----).

Fig 1

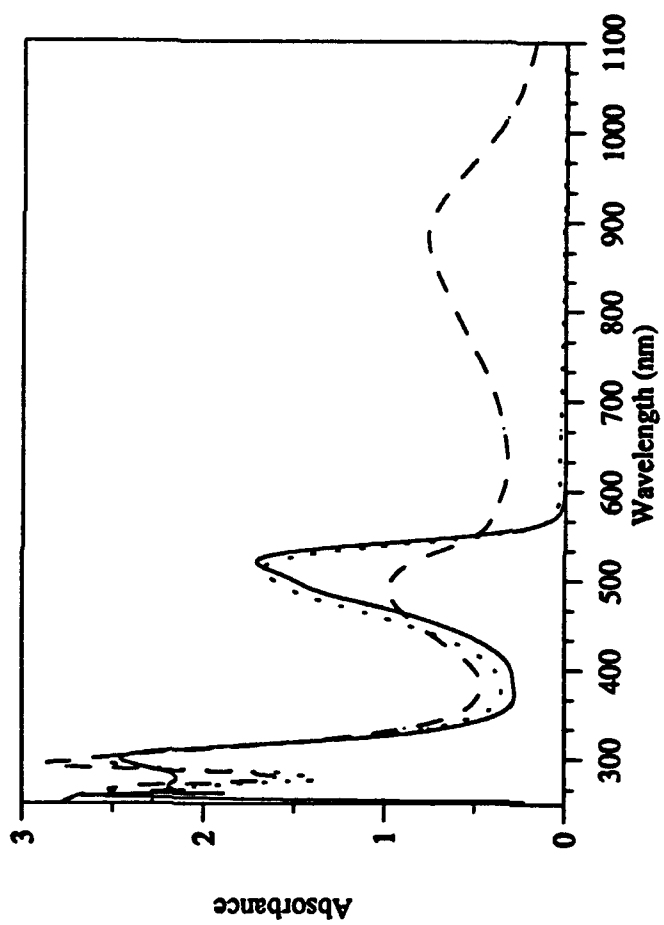


Fig 2



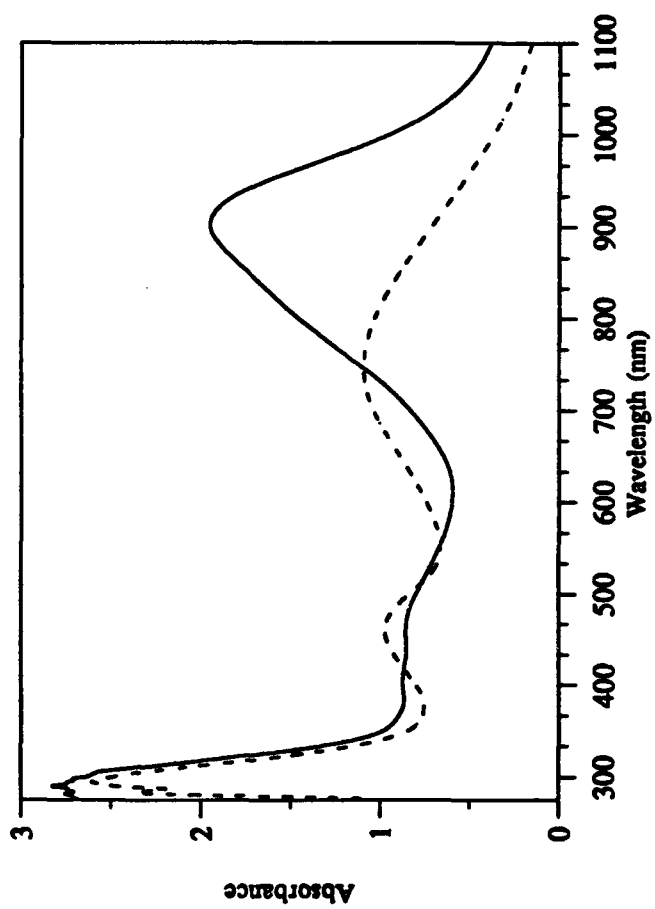


Fig 3

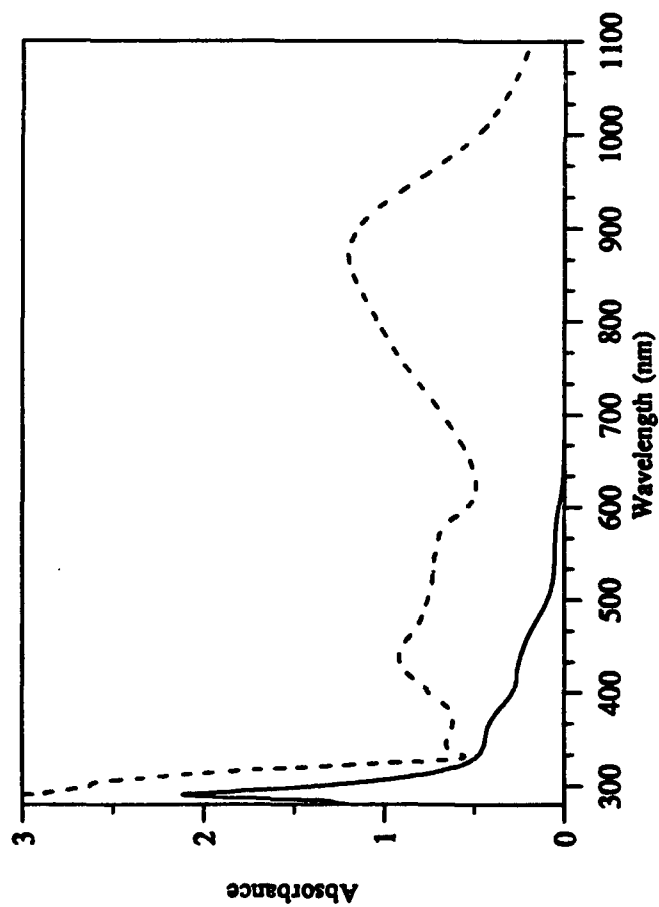


Scheme 1

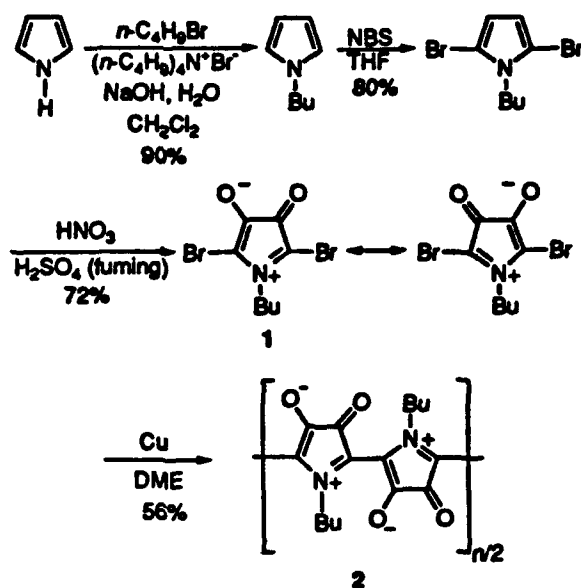

one-
column
format

Scheme 2

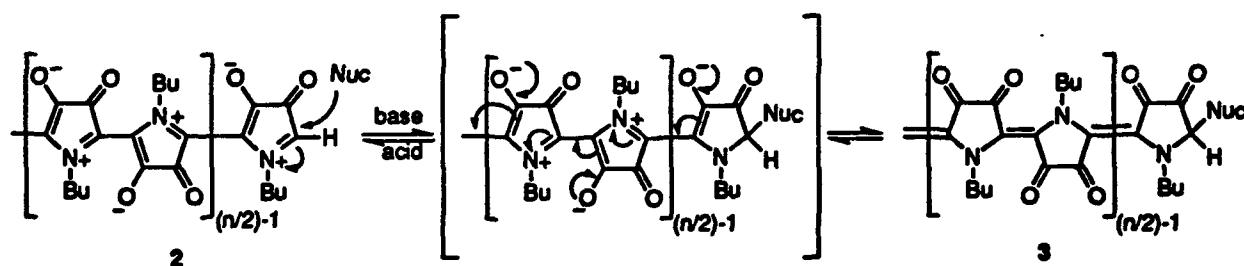

two-
column
format