

Final Report
Grant No. N00014-92-J-1580
May 1, 1992 - April 30, 1994

**A THEORETICAL ANALYSIS OF STRAIN IN GaN AND ITS
EFFECTS ON CARRIER CONDUCTIVITY**

Submitted to:

Dr. Max N. Yoder
Code ONR-312, Room #607
Office of Naval Research
800 N. Quincy Street
Arlington, VA 22217-5660

Submitted by:

Michael Shur
John Marhsall Money Professor

Report No. UVA/525467/EE95/101
December 1994

DEPARTMENT OF ELECTRICAL ENGINEERING



SCHOOL OF
ENGINEERING 
& APPLIED SCIENCE

19941213 033

University of Virginia
Thornton Hall
Charlottesville, VA 22903

DTIC QUALITY INSPECTED 1

UNIVERSITY OF VIRGINIA
School of Engineering and Applied Science

The University of Virginia's School of Engineering and Applied Science has an undergraduate enrollment of approximately 1,500 students with a graduate enrollment of approximately 600. There are 160 faculty members, a majority of whom conduct research in addition to teaching.

Research is a vital part of the educational program and interests parallel academic specialties. These range from the classical engineering disciplines of Chemical, Civil, Electrical, and Mechanical and Aerospace to newer, more specialized fields of Applied Mechanics, Biomedical Engineering, Systems Engineering, Materials Science, Nuclear Engineering and Engineering Physics, Applied Mathematics and Computer Science. Within these disciplines there are well equipped laboratories for conducting highly specialized research. All departments offer the doctorate; Biomedical and Materials Science grant only graduate degrees. In addition, courses in the humanities are offered within the School.

The University of Virginia (which includes approximately 2,000 faculty and a total of full-time student enrollment of about 17,000), also offers professional degrees under the schools of Architecture, Law, Medicine, Nursing, Commerce, Business Administration, and Education. In addition, the College of Arts and Sciences houses departments of Mathematics, Physics, Chemistry and others relevant to the engineering research program. The School of Engineering and Applied Science is an integral part of this University community which provides opportunities for interdisciplinary work in pursuit of the basic goals of education, research, and public service.

A Final Report
Grant No. N00014-92-J-1580
May 1, 1992 - April 30, 1994

**A THEORETICAL ANALYSIS OF STRAIN IN GaN AND ITS
EFFECTS ON CARRIER CONDUCTIVITY**

Submitted to:

Dr. Max N. Yoder
Code ONR-312, Room #607
Office of Naval Research
800 N. Quincy Street
Arlington, VA 22217-5660

Submitted by:

Michael Shur
John Marshall Money Professor

Accession For		
NTIS	CRA&I	☒
DTIC	TAB	☐
Unannounced		☐
Justification		
By		
Distribution /		
Availability Codes		
Dist	Avail. and/or Special	
A-1		

Department of Electrical Engineering
SCHOOL OF ENGINEERING AND APPLIED SCIENCE
UNIVERSITY OF VIRGINIA
CHARLOTTESVILLE, VIRGINIA

Report No. UVA/525467/EE95/101
December 1994

Copy No. _____

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1294, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave Blank)		2. REPORT DATE December 1994		3. REPORT TYPE AND DATES COVERED Final 5/1/92 - 4/30/94	
4. TITLE AND SUBTITLE A Theoretical Analysis of Strain In GaN and Its Effects on Carrier Conductivity				5. FUNDING NUMBERS N00014-92-J-1580	
6. AUTHOR(S) M. Shur, John Marshall Money Professor					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of Virginia, School of Engineering and Applied Science Department of Electrical Engineering Thornton Hall Charlottesville, VA 22903-2442				8. PERFORMING ORGANIZATION REPORT NUMBER UVA/525467/EE95/101	
9. SPONSORING MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research 800 N. Quincy Street Arlington, VA 22217-5660				10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES					
12a. DISTRIBUTION/AVAILABILITY STATEMENT				12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) We performed an ensemble Monte Carlo simulation of the electron transport in gallium nitride (GaN). Our calculation showed that intervalley electron transfer plays a dominant role in GaN in high electric fields leading to a strongly inverted electron distribution and to a large negative differential conductance. We found that, in a GaN-AlN-GaN SIS structure, the strain-induced electric fields can shift the flat band voltage and produce an accumulation region on one side and the depletion region on the other side of the AlN insulator. We used our theory, the current-voltage measurements and the capacitance-voltage measurements of the GaN-AlN-GaN SIS structures for quantitative characterization of the degree of the AlN film relaxation depending on the film thickness. Our results show that the 30 Å AlN film is slightly relaxed, the 60 Å film data show well-developed relaxation process, and the 100 Å structure is almost fully relaxed. Our data indicate that the low bound of the conduction band offset for the AlN/GaN heterointerface is close to 1 eV.					
14. SUBJECT TERMS Gallium nitride, aluminum nitride, electron transport, semiconductor-insulator-semiconductor structures, elastic strain relaxation, piezoeffect, current-voltage characteristics.				15. NUMBER OF PAGES 16	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT UL		

TABLE OF CONTENTS

	<u>Page</u>
I. THE ELECTRON TRANSPORT IN GaN	1
II. CHARGE INDUCED BY STRAIN AND C-V CHARACTERISTICS IN WURTZITE SIS STRUCTURES	3
III. THE ASYMMETRIC C-V AND THE ELASTIC STRAIN RELAXATION .	4
IV. GaN-AIN-GaN SIS: I-V CHARACTERISTICS	6
V. NOVEL PRESSURE SENSOR BASED ON GaN-AIN-GaN OR SiC-AIN-SiC SIS	8

I. The Electron Transport in GaN

We performed¹ an ensemble Monte Carlo simulation of the electron transport in gallium nitride (GaN). Our calculation showed that intervalley electron transfer plays a dominant role in GaN in high electric fields leading to a strongly inverted electron distribution and to a large negative differential conductance.

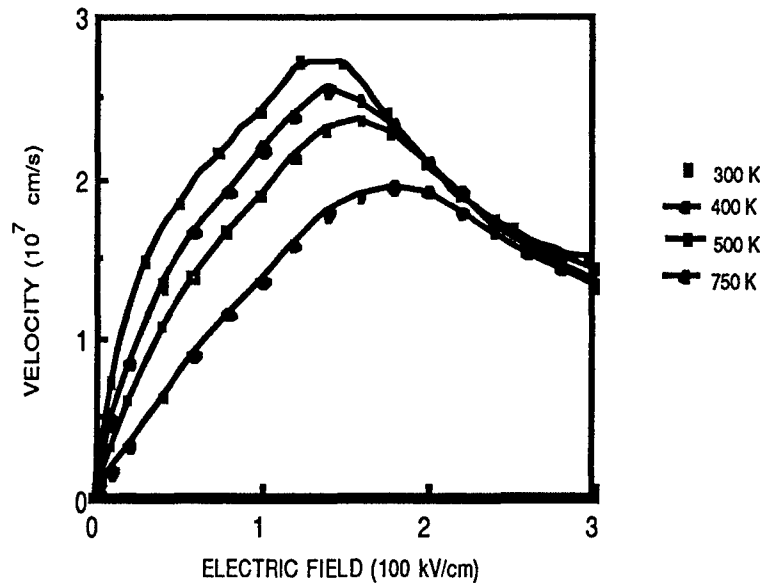


Figure 1. Electron Velocity in GaN as a Function of Electric Field for Different Temperatures.

We also derived an analytic expression for the polar optical momentum relaxation time for phonon energies larger than the thermal energy. This expression applies

¹B. Gelmont, K. Kim, and M. Shur, J. Appl. Phys., 74, 1818 (1993)

to many wide-gap semiconductors, such as GaN and SiC, at room temperature since these semiconductors have large polar optical phonon energies (on the order of 100 meV). The calculated mobility agrees well with the results of the Monte Carlo calculation.

II. Charge Induced by Strain and C-V Characteristics in Wurtzite SIS Structures.

We calculated the strain-induced electric field and charge distribution in such structures^{2, 3}. We found that, in a SIS structure grown along a (0001) crystallographic direction, the strain-induced electric fields can shift the flat band voltage and produce an accumulation region on one side and the depletion region on the other side of the AlN insulator. The surface charge density caused by the piezoeffect is on the order of 10^{12} cm^{-2} . As a consequence of the asymmetry in the space charge distribution, the capacitance-voltage characteristics of the SIS structure become asymmetrical. The asymmetrical shift of the C-V characteristics with respect to the origin is on the order of 1.5 V for a 30 Å AlN film. This asymmetry should vanish in a relaxed film.

² A. Bykhovski, B. Gelmont, and M. Shur, J. Appl. Phys., 74, 6734 (1993)

³ A. Bykhovski, B. Gelmont, and M. Shur, Appl. Phys. Letters, 63, 2243 (1993)

III. The Asymmetric C-V and the Elastic Strain Relaxation.

We used our theory and the capacitance-voltage measurements of the GaN-AlN-GaN SIS structures for quantitative characterization of the degree of the AlN film relaxation depending on the film thickness⁴. The starting point for the generation of misfit dislocation corresponds to $L \geq 30 \text{ \AA}$ (see Fig. 2).

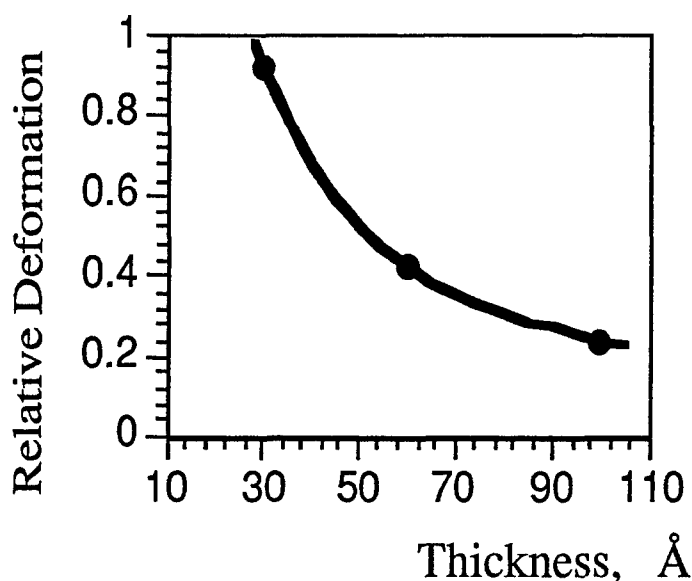


Figure 2. Relative Elastic Strain Tensor Component, $u_{xx}/u_{xx}(0)$, as a Function of AlN Thickness, L .

Here $u_{xx}(0) = (a_{\text{GaN}} - a_{\text{AlN}})/a_{\text{AlN}}$, a_i are lattice periods in the hexagonal plane. Circles are experimental data, solid line is interpolation. $N_d = 2 \cdot 10^{17} \text{ cm}^{-3}$

This conclusion is in agreement with experimental studies of strained-layer GaN/AlN superlattices⁵. Our data show that the 75% elastic strain relaxation

⁴A. Bykhovski, B. Gelmont, M. Shur, and A. Khan, in: Proceedings of the International Conference on Silicon Carbide and Related Materials, Inst. of Phys. Conf. Ser. Number 137, Inst. of Physics Publishing, Bristol and Philadelphia, p 691 (1994).

⁵Sitar Z., Paisley M. J., Yan B., Ruan J., Choyke W. J., and Davis R. F., 1990, J. Vac. Sci. Technol., B 8, 316.

GaN/AlN superlattices⁵. Our data show that the 75% elastic strain relaxation takes place at $L=100\text{\AA}$. The similar approach was applied to SiC/AlN/SiC SIS⁶. 2H(6H) SiC and wurtzite AlN were considered. We developed the characterization technique which can be used to determine the strains and (or) the doping concentrations from measured capacitance under zero bias.

⁵Sitar Z., Paisley M. J., Yan B., Ruan J., Choyke W. J., and Davis R. F., 1990, J. Vac. Sci. Technol., B 8, 316.

⁶A. Bykhovski, B. Gelmont, M. Shur, and M. Spencer, in: Proceedings of the International Semiconductor Device Research Symposium, Charlottesville, December 1-3, 1993, p. 581.

IV. GaN-AlN-GaN SIS: I-V Characteristics

We studied the elastic strain relaxation on the current-voltage (I-V) characteristics in SIS and estimated the AlN/GaN conduction band discontinuity from the measured I-V characteristics⁷.

To calculate the current in forward direction, we assumed that electrons are first activated above the energy corresponding to the depletion layer barrier and then tunnel through the AlN layer. We obtained good agreement between the theory and the experiment for $L = 100 \text{ \AA}$ assuming the uniform relaxation and found the low bound of AlN/GaN conduction band discontinuity at about 1 eV.

We showed that the non uniformity of the film relaxation may have a dramatic effect on the current-voltage characteristics. We explained our experimental data for thinner AlN films in the frame of simple model which assumes just two regions with different degree of relaxation in order to account for the relaxational non uniformity across the device cross-section. The portion of the cross-section with a lower degree of relaxation determines the I-V characteristics at high bias and the portion of the cross-section with a higher degree of relaxation determines the I-V characteristics at low bias. Using our approach, we obtained satisfactory agreement with the experimental data (see Fig. 3).

Our results show that the $30 \text{ \AA}$ AlN film is slightly relaxed, the $60 \text{ \AA}$ film data show well-developed non-uniform relaxation process, and the $100 \text{ \AA}$ structure is almost fully and uniformly relaxed.

In these films with $L=30 \text{ \AA} - 100 \text{ \AA}$ the areas of weak and strong relaxation coexist. The upper limit for the elastic strain relaxation obtained using I-V is in a satisfactory agreement with the corresponding data obtained from the measured C-V of the same structures⁴. However, the I-V characteristics are more sensitive to the non-uniformity in the barrier energies than the C-V characteristics.

⁷A. Bykhovski, B. Gelmont, M. Shur, and A. Khan, J. of Applied Physics., February (1995), to be published.

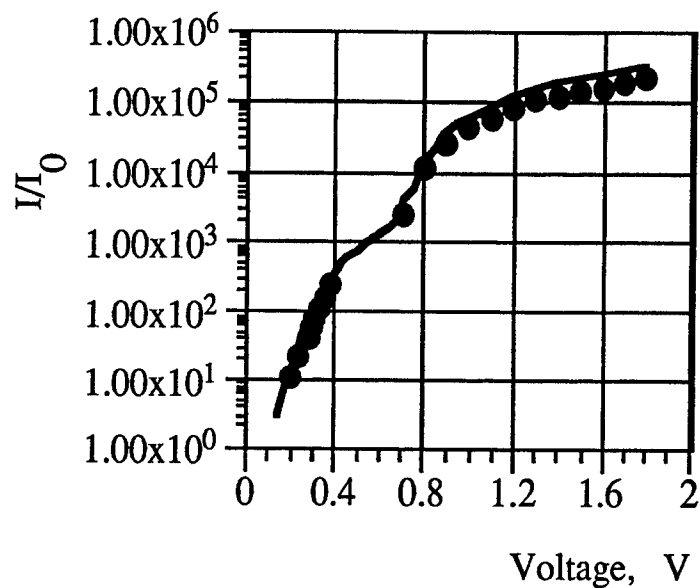


Figure 3.

Forward Current in GaN-AlN-GaN SIS.

$L = 30 \text{ \AA}$.

Effective barrier is 0.9 eV; area is $31400 \text{ \mu m}^2$; series resistance is $10^5 \text{ \Omega}$; donor concentration is $2 \times 10^{17} \text{ cm}^{-3}$. $I_0 = 0.034 \text{ nA}$, $j_0 = I_0/S = 1.08 \text{ mA/m}^2$. Solid line - calculations; points are experimental data.

V. Novel Pressure Sensor Based on GaN-AlN-GaN or SiC-AlN-SiC SIS

We proposed⁸ a new sensor which is capable of operating at a very high temperature and has a large sensitivity. It can be fabricated using SiC-AlN-SiC or GaN-AlN-GaN Semiconductor-Insulator-Semiconductor structures. The change in the applied pressure can result in decreasing (or increasing) the current through SIS structure due to piezoeffect (see Fig. 4).

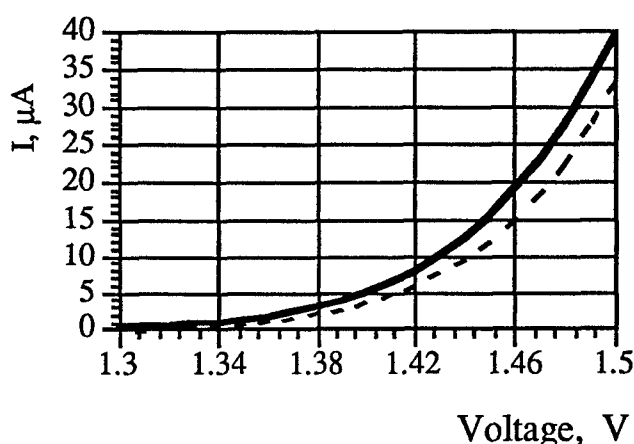


Figure 4. Forward Current Through the SIS Structure as a Function of Voltage.
 Solid line: I-V without external pressure;
 Dashed line: force 0.01 N applied to the surface of SIS.
 Doping level is $2 \times 10^{17} \text{ cm}^{-3}$. Area is $100 \text{ } \mu\text{m}^2$, series resistance is $10^3 \text{ } \Omega$.

Applied pressure creates elastic strain in the barrier layer, which, in turn, changes the strain-induced electric field and, therefore, the shape of the barrier. The sensitivity of the device can be optimized by changing doping levels, a series resistance, temperature, the thickness of the barrier layer and the composition.

⁸A. Bykhovski, M. Shur, and M. Spencer, Jan. 1994.

ABSTRACT:

"MONTE CARLO SIMULATION OF ELECTRON TRANSPORT IN GALLIUM NITRIDE" by B. Gelmont, K. Kim, and M. Shur.

The results of an ensemble Monte Carlo simulation of the electron transport in gallium nitride (GaN) are presented. The calculation shows that intervalley electron plays a dominant role in GaN in high electric fields leading to a strongly inverted electron distribution and to a large negative differential conductance. An analytic expression for the polar optical momentum relaxation time for phonon energies larger than the thermal energy is also derived. This expression applies to many wide-gap semiconductors, such as GaN and SiC, at room temperature since these semiconductors have large polar optical phonon energies (on the order of 100 meV). The calculated mobility agrees well with the results of the Monte Carlo calculation.

ABSTRACT:

"CURRENT-VOLTAGE CHARACTERISTICS OF STRAINED PIEZOELECTRIC STRUCTURES" by A. Bykhovski, B. Gelmont, M. Shur, and A. Khan, Journal of Applied Physics, to be published.

We present experimental and theoretical studies of the current-voltage characteristics of symmetrically doped n-type GaN-AlN-GaN Semiconductor-insulator-semiconductor (SIS) structures. The asymmetry caused by the strain-induced electric field leads to the depletion layer barrier in addition to the barrier presented by a thin insulating layer of AlN. We show that the tunnel current depends on the degree of the elastic strain relaxation which, in turn, is related to

the AlN film thickness, and that this dependence provides quantitative information about the film relaxation. This characterization technique is compared with the capacitance-voltage characterization of the SIS structures. Our data indicate the low bound of conduction band discontinuity of about 1 eV at AlN/GaN heterointerface.

ABSTRACT:

"THE INFLUENCE OF THE STRAIN-INDUCED ELECTRIC FIELD ON THE CHARGE DISTRIBUTION IN GaN-AlN-GaN STRUCTURE" by A. Bykhovski, B. Gelmont , and M. Shur published in Journal of Applied Physics, 74, 6734 (1993).

We show that strongly pronounced piezoelectric properties play a key role in GaN-AlN-GaN Semiconductor-Insulator-Semiconductor (SIS) and related structures. In sufficiently thin AlN layers, the lattice constant mismatch is accommodated by internal strains rather than by the formation of misfit dislocations. These lattice-mismatch-induced strains generate polarization fields. We demonstrate that, in a GaN-AlN-GaN SIS structure with the growth axis along a (0001) crystallographic direction, the strain-induced electric fields can shift the flat band voltage and produce an accumulation region on one side and the depletion region on the other side of the AlN insulator. Which side of the insulator the accumulation region is produced at, depends on the type of the atomic plane at the heterointerface (Ga or N). The surface charge density caused by the piezoeffect is on the order of 10^{12} cm^{-2} . As a consequence of the asymmetry in the space charge distribution, the capacitance-voltage characteristics of the SIS structure become asymmetrical. The asymmetrical shift of the C-V characteristics

with respect to the origin is on the order of 1.5 V for a 30 Å AlN film. This asymmetry should vanish in a relaxed film. Hence, the capacitance-voltage measurements of the GaN-AlN-GaN SIS structures can be used for quantitative characterization of the degree of the AlN film relaxation depending on the film thickness. This and related techniques should become an important tool for the characterization of piezoelectric layered semiconductor films.

ABSTRACT:

"STRAIN AND CHARGE DISTRIBUTION IN GaN-AlN-GaN SEMICONDUCTOR-INSULATOR-SEMICONDUCTOR STRUCTURE FOR ARBITRARY GROWTH ORIENTATION" by A. Bykhovski, B. Gelmont, and M. Shur, Appl. Phys. Letters, 63, 2243 (1993).

We demonstrate that, in a GaN-AlN-GaN Semiconductor-Insulator-Semiconductor (SIS) structure, the strain-induced electric fields across the interface depend on the angle, θ , between the c-axis and the growth direction. The magnitude of the strain induced polarization has a maximum in (0001) crystallographic direction ($\theta=0^\circ$) and a subsidiary maximum near $\theta=70^\circ$. This angular dependence is a unique feature of wurtzite-type structures. Considering θ as an independent parameter for device design, one can obtain structures with flat band voltage shift from 0 to 1.5V for 30Å AlN film, with different positions of accumulation-depletion regions, and with electron (hole) charge varying from 0 to more than 10^{12} cm^{-2} .

DISTRIBUTION LIST

1 - 3	Dr. Max N. Yoder Code ONR-312, Room #607 Office of Naval Research 800 N. Quincy Street Arlington, VA 22217-5660 (703) 696-4218
4	Mr. Michael Karp Administrative Contracting Officer Office of Naval Research Resident Representative 101 Marietta Tower, Suite 2805 101 Marietta Street Atlanta, GA 30323-0008
5	Director Attention: Code 2627 Naval Research Laboratory Washington, DC 20375
6 - 7	Defense Technical Information Center S47031 Building 5, Cameron Station Alexandria, VA 22312
8 - 9	M. Shur
*	Postaward Research Administration
10 - 11	H. Earnhardt, Clark Hall
12	SEAS Preaward Administration Files
*	Cover Letter Only

JO#6087:pa