PHOTOGRAPH THIS SHEET

DTIC ACCESSION NUMBER

LEVEL

INVENTORY

WL-TR-94-4124

DOCUMENT IDENTIFICATION

Apr 97

DISTRIBUTION STATEMENT

DISTRIBUTION STATEMENT A
Approved for public release;
Distribution Unlimited

ACCESSION FOR

NTIS	GRA&I	☑
DTIC	TRAC	☐
UNANNOUNCED		☐
JUSTIFICATION		

BY

DISTRIBUTION/

AVAILABILITY CODES

DISTRIBUTION	AVAILABILITY AND/OR SPECIAL	
A-1		

DISTRIBUTION STAMP

DTIC
ELECTE
DEC 21 1994
S C D

DATE ACCESSIONED

DATE RETURNED

DATE RECEIVED IN DTIC

REGISTERED OR CERTIFIED NUMBER

PHOTOGRAPH THIS SHEET AND RETURN TO DTIC-FDAC

DTIC FORM 70A APR 87

DOCUMENT PROCESSING SHEET

PREVIOUS EDITIONS MAY BE USED UNTIL STOCK IS EXHAUSTED

19941219 100

WL-TR-94-4124

TABLES OF DIELECTRIC MATERIALS, VOL V



A. VON HIPPEL
W. B. WESTPHAL

LABORATORY FOR INSULATION RESEARCH
MASSACHUSETTS INSTITUTE OF TECHNOLOGY
CAMBRIDGE MA

APRIL 1957

FINAL REPORT

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION IS UNLIMITED.

MATERIALS DIRECTORATE
WRIGHT LABORATORY
AIR FORCE SYSTEMS COMMAND
WRIGHT PATTERSON AFB OH 45433-7734

DTIC QUALITY INSPECTED 1

NOTICE

WHEN GOVERNMENT DRAWINGS, SPECIFICATIONS, OR OTHER DATA ARE USED FOR ANY PURPOSE OTHER THAN IN CONNECTION WITH A DEFINITELY GOVERNMENT-RELATED PROCUREMENT, THE UNITED STATES GOVERNMENT INCURS NO RESPONSIBILITY OR ANY OBLIGATION WHATSOEVER. THE FACT THAT THE GOVERNMENT MAY HAVE FORMULATED OR IN ANY WAY SUPPLIED THE SAID DRAWINGS, SPECIFICATIONS, OR OTHER DATA, IS NOT TO BE REGARDED BY IMPLICATION, OR OTHERWISE IN ANY MANNER CONSTRUED, AS LICENSING THE HOLDER, OR ANY OTHER PERSON OR CORPORATION; OR AS CONVEYING ANY RIGHTS OR PERMISSION TO MANUFACTURE, USE, OR SELL ANY PATENTED INVENTION THAT MAY IN ANY WAY BE RELATED THERETO.

THIS REPORT IS RELEASABLE TO THE NATIONAL TECHNICAL INFORMATION SERVICE (NTIS). AT NTIS, IT WILL BE AVAILABLE TO THE GENERAL PUBLIC, INCLUDING FOREIGN NATIONS.

THIS TECHNICAL REPORT HAS BEEN REVIEWED AND IS APPROVED FOR PUBLICATION.

Robert J. Ondercin

ROBERT J. ONDERCIN
Electronic & Optical Mat'ls Branch
Electromagnetic Mat'ls & Surv. Div.

Robert L. Denison

ROBERT L. DENISON, Chief
Electronic & Optical Mat'ls Branch
Electromagnetic Mat'ls & Surv. Div.

William R Woody

WILLIAM R. WOODY, Chief
Electromagnetic Mat'ls & Surv. Div.
Materials Directorate

IF YOUR ADDRESS HAS CHANGED, IF YOU WISH TO BE REMOVED FROM OUR MAILING LIST, OR IF THE ADDRESSEE IS NO LONGER EMPLOYED BY YOUR ORGANIZATION PLEASE NOTIFY WL/MLPO, BLDG 651, 3005 P ST STE 6, WPAFB OH 45433-7707, TO HELP MAINTAIN A CURRENT MAILING LIST.

COPIES OF THIS REPORT SHOULD NOT BE RETURNED UNLESS RETURN IS REQUIRED BY SECURITY CONSIDERATIONS, CONTRACTUAL OBLIGATIONS, OR NOTICE ON A SPECIFIC DOCUMENT.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE	3. REPORT TYPE AND DATES COVERED
	APR 1957	FINAL

4. TITLE AND SUBTITLE

TABLES OF DIELECTRIC MATERIALS, VOL V

5. FUNDING NUMBERS

C 1841 -10- -
PE
PR
TA
WU

6. AUTHOR(S)

A. VON HIPPEL
W. B. WESTPHAL

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)

LABORATORY FOR INSULATION RESEARCH
MASSACHUSETTS INSTITUTE OF TECHNOLOGY
CAMBRIDGE MA

8. PERFORMING ORGANIZATION REPORT NUMBER

119

9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)

MATERIALS DIRECTORATE
WRIGHT LABORATORY
AIR FORCE SYSTEMS COMMAND
WRIGHT PATTERSON AFB OH 45433-7734

10. SPONSORING / MONITORING AGENCY REPORT NUMBER

WL-TR-94-4124

11. SUPPLEMENTARY NOTES

12a. DISTRIBUTION / AVAILABILITY STATEMENT

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION IS UNLIMITED.

12b. DISTRIBUTION CODE

13. ABSTRACT *(Maximum 200 words)*

This report is a compilation of dielectric materials properties. It was originally published in April 1957, by the Laboratory for Insulation Research, Massachusetts Institute of Technology. The report includes (1) dielectric constant and loss tangent data as a function of temperature and frequency, (2) low field strength data at fixed temperatures as a function of frequency, hysteresis loops and saturation magnetization for ferromagnetic dielectrics and (3) attenuation characteristics of ferrites, conducting ceramics and plastics, carbon-plastic mixtures and magnetic-plastic mixtures.

14. SUBJECT TERMS

DIELECTRIC CONSTANT, LOSS TANGENT, FREQUENCY, TEMPERATURE SATURATION MAGNETIZATION

15. NUMBER OF PAGES

281

16. PRICE CODE

17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT	20. LIMITATION OF ABSTRACT
UNCLASSIFIED	UNCLASSIFIED	UNCLASSIFIED	UL

ERRATA

Tables of Dielectric Materials, Vol. V

Page viii, line 6, for "0.1" read "< 0.1."

" x, line 8, for "0.005" read "< 0.005"; for "1" read "> 1";
line 10, for "0.002" read "< 0.002."

" 2, line 3 from bot., for "1.3," "1.7," "4.8" read "13," "1.3," "1.7."

" 4, line 11, for "0.004" read "0.044"; line 13, delete "268" and "21.4."

" 5, lines 6 and 7, raise to correspond with "Corning 7910."

" 7, line 3 from bot., for ".3.68" read "3.68."

" 8, line 4, for "-275" read "275"; line 5, for "33.27" read "3.27."

" 11, line 6, for "--31" read "31."

" 13, line 3, for "to film" read "$\perp$ to film"; lines 9 and 11 from bottom of Table, change single to double asterisks.

" 14, line 8, for "4.84" read "3.84."

" 161 and 165, "Note," for "K_m" read "κ^*_m."

" 174, line 2, delete " "Fe."

" 175, line 2, for "Cerqmivs" read "Ceramics."

" 245, line 9, first column, for "Iv-58" read "IV-58."

" 247, line 19, second column, for "159-175" read "159-176."

" 249, line 6 from bot., first column, for "133-139, 142-158, 177-180" read "133-136, 138, 139, 142-158, 177, 179, 180"; second column, line 2, for "V-140, 141" read "V-137, 140, 141"; line 3, for "176, 181, 182" read "176, 178, 181, 182."

Laboratory for Insulation Research
Massachusetts Institute of Technology

In addition to the printed errata the following errors have come to our attention:

Page 6, Boron nitride, add these tan δ's:

f	tan δ
$1x10^2$	10.3
$1x10^3$	6.5
$1x10^4$	4.2
$1x10^5$	3
$1x10^6$	2.0
$1x10^7$	1.4
$1x10^8$	0.92

Page 39, tan δ at $f = 10^{10}$ should be:

T^oC	tan δ
26	0.00026
116	0.00029
206	0.00034
302	0.00044
412	0.00058
457	0.00069
499	0.00080

Page 52, "Wesgo" Al-300:

$f = 9.5x10^9$ instead of $f = 9.5x10^{10}$;

tan δ scale should read:

0.0006

0.0004

0.0002

TABLES OF DIELECTRIC MATERIALS

VOLUME V

Laboratory for Insulation Research
Massachusetts Institute of Technology
Cambridge, Massachusetts

Contract Nonr-1841(10)

April, 1957

The work reported in this document was made possible through support extended to the Massachusetts Institute of Technology, Laboratory for Insulation Research, jointly by the Navy Department (Office of Naval Research), the Army Signal Corps, the Air Force (Air Materiel Command), and the Ordnance Materials Research Office under ONR Contract Nonr-1841(10), NR-017-421. Reproduction of this article in whole or in part is permitted for any purpose of the United States Government.

Table of Contents

	Page
Introduction	v
Dielectric Parameters	viii
Measurements and Accuracy	x
I. Tabulated Dielectric Data at Room Temperature	1
A. Solids, inorganic	1
1. Crystals	1
2. Ceramics	1
a. Aluminas	1
b. Ferrites	4
c. Steatite	4
d. Wollastonites	4
e. Zircon	5
3. Glasses, including devitrified glasses	5
4. Miscellaneous inorganics	6
B. Solids, organic	8
1. Plastics (including plastics with fillers, laminates)	8
a. Phenolic resins	8
b. Melamine-formaldehyde	8
c. Cellulose derivatives	9
d. Silicone resins	9
e. Polyvinyl resins	10
(1) Polyethylene	10
(2) Polyvinyl chloride-acetate	10
(3) Polychlorotrifluoroethylene	10
(4) Polytetrafluoroethylene	10

Table of Contents (cont.)

Page

(5) Polyacrylate 10

(6) Polystyrene 10

(7) Miscellaneous polystyrenes . . . 11

(8) Styrene copolymers, cross-linked 11

f. Polyesters 12

g. Epoxy resins 14

h. Miscellaneous plastics 16

2. Waxes 16

3. Miscellaneous organics 17

C. Liquids 18

1. Inorganic 18

2. Organic 18

a. Aliphatic 18

b. Aromatic 19

c. Petroleum oil 19

d. Silicones 20

D. Gases 20

II. Supplement

A. Materials measured too late for inclusion in Section I 21

B. Dielectric constant at room temperature vs. density 23

III. Data at Fixed Frequencies as a Function of Temperature 26

A. Solids, inorganic 26

1. Crystals 26

2. Ceramics 30

Table of Contents (cont.)

Page

a. Aluminas 30

b. Beryllias 52

c. Ferrites 54

d. Steatites 55

e. Wollastonite 58

f. Zircons 59

3. Glasses 62

4. Miscellaneous inorganics 74

B. Plastics 80

1. Phenolics 80

2. Melamine-formaldehyde 88

3. Polyamide resin 89

4. Cellulose derivatives 90

5. Silicone resins 93

6. Polychlorotrifluoroethylene 102

7. Polytetrafluoroethylene 104

8. Styrene copolymers 105

9. Polyesters 106

10. Alkyd resins 112

11. Epoxy resins 114

C. Elastomers 127

D. Liquids 130

IV. Ferromagnetic Dielectrics 132

A. Low field strength data at fixed temperatures as a function of frequency 133

1. Nickel ferrite, single crystals 133

Table of Contents (cont.)

Page

2. Cobalt ferrite, high density ceramic . . . 136
3. Lithium-nickel ferrite ceramic 137
4. Magnesium ferrite, high density ceramic . . 138
5. Magnesium-manganese ferrite ceramics . . 139
6. Magnesium-manganese-zinc ferrite ceramic 141
7. Nickel ferrite, high density ceramic . . . 142
8. Nickel-zinc ferrites, high density ceramics 144
9. Zinc ferrite, high density ceramic . . . 158
10. Commercial ferrite ceramics 159

B. Hysteresis loops and saturation magnetization . 177

1. Cobalt ferrite, high density ceramic . . . 177
2. Lithium-nickel ferrite ceramic 178
3. Magnesium ferrite, high density ceramic . . 179
4. Magnesium-manganese ferrite ceramics . 180
5. Magnesium-manganese-zinc ferrite, ceramic 182
6. Nickel ferrite, high density ceramic . . . 183
7. Nickel-zinc ferrite, high density ceramics . 184
8. Commercial ferrite ceramics 191
9. Magnetic plastic mixture 205

V. Attenuator Characteristics (attenuation, phase shift, and intrinsic impedance) 206

A. Ferrites 206
B. Conducting ceramics 234
C. Conducting plastics 235
D. Carbon-plastic mixtures 237
E. Magnetic plastic mixtures 242

Company Index 245

Materials Index 253

Tables of Dielectric Materials

Volume V

Laboratory for Insulation Research
Massachusetts Institute of Technology
Cambridge, Massachusetts

During World War II the Laboratory for Insulation Research assumed, in addition to other tasks, the responsibility of acting as a clearing house for dielectric information. It developed measurement techniques over wide ranges of frequency and temperature, provided data on materials of strategic importance and summarized the results in the "Tables of Dielectric Materials."

Volumes I and II were issued during the war. The termination of hostilities, however, did not end our obligation. Government and Industry relied on these data, and the idea had become entrenched that materials of general interest could be measured in our laboratory free of charge in return for background information required for the defense effort. Volume III was issued in 1948, and our clearing house activity stepped up when the outbreak of the Korean war emphasized the precariousness of the political situation. Volume IV, released in January 1953, summarized in expanded measurements all materials of importance at that time and was made generally available as Appendix to the book "Dielectric Materials and Applications" (Technology Press and John Wiley and Sons, New York, 1954). In the interim periods, the accumulating information aided Government agencies and industrial laboratories in the selection and development of dielectrics under Government contracts.

Since 1953 the missile age has arrived with its demands for high-temperature dielectrics. At the same time the concepts of "Molecular

Engineering," on which the Laboratory for Insulation Research was founded, are rapidly becoming public property: dielectrics are being made to order for an increasing number of new devices. These trends are reflected in Volume V of the "Tables" by extension to high-temperatures (Sec. III), ferromagnetics (Sec. IV) and attenuator characteristics (Sec. V).

Like its predecessors, Volume V is a storage bin of practical information, ill-adapted for theoretical analysis. Here are radome materials and glass cloth; jet fuel and compressed gases; Scotch tape, Kraft paper and Sauereisen cement, to mention only some of the more outlandish representatives. Here is demonstrated that impure raw materials cause inferior high-temperature performance and that overheating produces rapid degradation. There are also examples of beneficial action of heating in driving out detrimental moisture and volatile compounds. Trends are revealed for the development of better materials, and faulty manufacturing practices are exposed for remedial action. Our task here is an unbiased presentation of data, which leaves the users of the "Tables" free to draw their own conclusions.

A true dielectric analysis of materials requires a different approach: accurately defined materials; controlled variation of composition and structure; careful investigation of the influence of manufacturing parameters; and a comparison of the properties of multicrystalline materials with those of single crystals. This arduous task has been started in our laboratory for ferromagnetic semiconductors by a careful ceramics study of square-loop materials (G. Economos, Tech. Rep. 78, May, 1954; J. Amer. Ceram. Soc., July through November, 1955); in an extensive broad-band investigation of ferrites from d.c. to the ultraviolet (A. von Hippel, W.B. Westphal and P.A. Miles, "Dielectric Spectroscopy of Ferromagnetic Semiconductors," Tech. Rep. 97, July, 1955, revised for Revs. Mod. Phys., July, 1957);

and by a detailed analysis of a special type of relaxation spectrum identified in ferrites (D. J. Epstein, "Domain-Wall Relaxation in Ferrites," Papers presented at the Conference on Magnetism and Magnetic Materials, Boston, Mass., Oct. 16-18, 1956, Amer. Inst. Elec. Engrs. T-91, 1957, p. 493).

The development of "Dielectric Spectroscopy" into a powerful tool of nondestructive analysis for the whole field of "Molecular Science and Engineering" should receive top priority in the use of our resources from now on. We intend therefore to terminate the service "Tables of Dielectric Materials" by the end of this year; a Volume VI will summarize ferroelectric and residual data. We hope that some independent and unbiased agency will continue this work of evaluating materials and acting as a clearing house for dielectric information.

Our venture was made possible through the ingenuity and indefatigable efforts of Mr. W.B. Westphal, group leader of the dielectric measurements group. Mrs. Barbara Beal East, his able co-worker for several years, measured most of the low field-strength data, supported in recent months by Mrs. Rhoda Yarkin. Mrs. Ann Miller and Frank Bispham gave technical assistance, and Miss Aina Sils and John Mara were of great help in the preparation of the final manuscript. The hysteresis data of Sec. IV were obtained by B. Frakiewicz with F. Bispham and under the general direction of Prof. D.J. Epstein, group leader of the ferromagnetics group.

The Laboratory for Insulation Research has operated under the joint sponsorship of the Navy Department (Office of Naval Research), the Army Signal Corps, the Air Force (Air Matériel Command), and the Ordnance Materials Research Office for many years in an atmosphere of mutual trust and understanding; we gratefully acknowledge this support.

A. von Hippel

Dielectric Parameters

1. ϵ'/ϵ_o, the dielectric constant or permittivity relative to vacuum, also designated in the literature as K, κ_e, κ', ϵ, ϵ', D.C., etc.
2. κ', same as ϵ'/ϵ_o.
3. tan δ, the dielectric loss tangent or dissipation factor, also designated in the literature as DF, $1/Q$, and when losses are low (0.1) as power factor or cos θ.
4. tan δ_d or tan δ_e, same as tan δ.
5. ϵ''/ϵ_o, the dielectric loss factor relative to vacuum, also designated in the literature as κ'', ϵ''. L.F., etc.
6. κ'', same as ϵ''/ϵ_o.
7. μ'/μ_o, the magnetic permeability relative to vacuum, also designated in the literature as μ', μ_R, μ_o, κ'_m.
8. κ'_m, same as μ'/μ_o.
9. tan δ_m, the magnetic loss tangent, also designated in the literature as $1/Q$.
10. μ''/μ_o, the magnetic loss factor in analogy to the dielectric loss factor; also designated in the literature as μ'', μ_I, κ''_m.
11. κ''_m same as μ''/μ_o.
12. $\kappa''/(\kappa'_m)^2$, a figure of merit for core materials, also designated in the literature as loss factor, $1/\mu'Q$.
13. tan δ_t, the total loss tangent, the sum of tan δ_d plus tan δ_m. Relations between parameters are discussed in Vol. IV. The ferromagnetic sections use the parameter κ''_m instead of tan δ_m, which becomes clumsy in the frequency region where κ' is close to zero or negative.
14. ρ, the a-c volume resistivity in ohm-cm.
15. σ, the a-c volume conductivity in mho/m.
16. α, the attenuation constant for propagation in free space in decibel per cm.

17. β/β_o, the phase constant relative to vacuum for propagation in free space.

18. $|Z|$, the magnitude of the intrinsic impedance relative to vacuum for propagation in free space.

19. θ, the angle of the intrinsic impedance.

Measurements and Accuracy

The measurements have been made, in general, on only one batch of the material and refer, unless otherwise specified, to samples measured at room temperature (25 to 26°C) and room humidity (30 to 50% R.H.). Due to the wide variety of materials and improvements in techniques, no figures of general validity can be given concerning the accuracy of these measurements. For ϵ'/ϵ_o, the nominal accuracy is $\pm 2\%$; the accuracy trends are toward $\pm 1\%$ for rigid, low-loss materials (tan δ 0.005) and $\pm 5\%$ for high-loss materials (tan δ 1). For tan δ_d, the nominal accuracy is $\pm 5\%$; for high-loss materials, the error may be $\pm 10\%$. For very low-loss materials (tan δ 0.002), the accuracy is ± 0.0001 when the losses are given as multiples of 0.0001. When the loss is expressed in multiples of 0.00001, the error may be ± 0.00003. For μ'/μ_o, the nominal accuracy is $\pm 5\%$, for tan δ_m, $\pm 10\%$.

Field strengths. The linear dielectrics, those normally not field-strength sensitive, were measured at field strengths of approximately 50 volts per cm. in the frequency range 10^2 to 10^8 c/s and at lower field strengths at higher frequencies.

The ferromagnetic materials, unless otherwise noted, were measured at field strengths in their linear region. The values thus measured are the initial permeability.

For laminates, which are in general not isotropic, the direction of the electric field is perpendicular to the plane of the laminate for frequencies in the range 10^2 to 3×10^8 c/s and parallel for higher frequencies unless otherwise specified.

Some metal-loaded materials have been measured which are slightly diamagnetic, but are not sufficiently homogeneous for precise separation of μ^* and ϵ^*. For these the product of dielectric constant and permeability and the sum of the loss tangents is given.

I. Tabulated Dielectric Data at Room Temperature (25 to 26°C)

Values of tan δ are multiplied by 10^4; frequency given in c/s.

		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
A. Solids, inorganic															
1. Crystals															
Aluminum oxide, sapphire[a]	ϵ'/ϵ_o	9.53	9.53	9.53	9.53	9.53	9.53	9.53	9.53	----	----	----	----	9.5	
(field ⊥ optical axis)	tan δ	< 10	< 2	< 10	< 10	< 10	< 10	< 10	< 1	----	----	----	----	< 20	
(field ∥ optical axis)	ϵ'/ϵ_o	11.53	11.53	11.53	11.53	11.53	11.53	11.53	11.53						
	tan δ	< 10	< 2	< 10	< 10	< 10	< 10	< 10	< 1						
Barium titanate, hexagonal[b]	ϵ'/ϵ_o	-----	----	59											
(field ⊥ optical axis)	tan δ	----	----	< 40											
(field ∥ optical axis)	ϵ'/ϵ_o	249	247	246	244										
	tan δ	62	41	27	15										
Calcium fluoride[b]	ϵ'/ϵ_o	----	6.82												
	tan δ	----	< 10												
Carbon, diamond[c]	ϵ'/ϵ_o	----	----	5.68											
	tan δ	----	----	< 2											
Cesium bromide[b]	ϵ'/ϵ_o	6.62	6.62	6.62	6.62										
	tan δ	2	< 1	< 1	< 2										
Cesium iodide[b]	ϵ'/ϵ_o	5.97	5.97	5.97	5.97										
	tan δ	10	6	4	< 2										
Potassium chloride[d]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	4.75			
	tan δ	----	----	----	----	----	----	----	----	----	----	1.1			
Thallium chloride[b]	ϵ'/ϵ_o	----	31.9												
	tan δ	----	380												
2. Ceramics															
a. Aluminas															
"AlSiMag" 491 (blue)[e]	ϵ'/ϵ_o	7.8	7.8	7.8	7.8	7.8	7.8	7.8	7.8	----	----	7.73			
	tan δ	11	9.8	9.5	9.4	7.4	5.8	7.8	9.2	----	----	13			
"AlSiMag" 513 (pink)[e]	ϵ'/ϵ_o	8.0	8.0	8.0	8.0	8.0	8.0	8.0	8.0	----	----	7.97			
	tan δ	9.7	22	18	9.2	7.9	11	15	16	----	----	15			

a. Linde Air. b. Lab. Ins. Res. c. Data of S. Whitehead and W. Hackett, Proc. Phys. Soc. 51, 173 1939. d. Harshaw. e. Amer. Lava (dry values).

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I A 2a. Aluminas (cont.)		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
"AlSiMag" 544[a**]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	5.80	----	----	5.80
	tan δ	----	----	----	----	----	----	----	----	----	----	10	----	----	10
"AlSiMag" 576[a]	ϵ'/ϵ_o	8.0	8.0	8.0	8.0	8.0	8.0	8.0	8.0	----	----	7.97			
	tan δ	10	7.5	5.5	4.2	3.4	4.0	6.4	7.9	----	----	15			
"AlSiMag" 614[a]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	10.0			
	tan δ	----	----	----	----	----	----	----	----	----	----	8			
Coors AL-100[b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	6.47			
	tan δ	----	----	----	----	----	----	----	----	----	----	0.9			
Coors AI-200[b] (1954 sample)	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	8.78			
	tan δ	----	----	----	----	----	----	----	----	----	----	10.4			
Corning JD-40[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	----	8.25		
	tan δ	----	----	----	----	----	----	----	----	----	----	----	38		
Corning JD-82[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	7.85			
	tan δ	----	----	----	----	----	----	----	----	----	----	18			
Corning JB-123[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	8.02			
	tan δ	----	----	----	----	----	----	----	----	----	----	20			
Corning WD-131[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	7.45			
	tan δ	----	----	----	----	----	----	----	----	----	----	25			
Corning JB-183[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	----	8.22		
	tan δ	----	----	----	----	----	----	----	----	----	----	----	30		
Diamonite B-890[d]	ϵ'/ϵ_o	9.25	9.25	9.25	9.25	9.25	9.25	9.25	9.25	9.23	9.20	9.15*			
	tan δ	9	5.4	6.8	7	6	< 1	< 1	3	5.8	9.1	10*			
Diamonite P-3142[d]	ϵ'/ϵ_o	9.60	9.60	9.60	9.60	9.60	9.60	9.60	9.60	9.53	9.42	9.36			
	tan δ	3.3	1.8	1.4	< 1	1.5	4.5	4.2	2.5	4.0	6.0	15			
Diamonite P-3459[d]	ϵ'/ϵ_o	12.8	12.1	10.7	9.43	9.13	9.10	9.10	9.10	9.08	9.05	9.03			
	tan δ	290	577	953	585	120	1.3	1.7	4.8	4.8	8.0	15			

a. Amer. Lava (dry values). b. Coors (dry value). c. Corning. d. Diamonite.

*Freq. = $9.3x10^9$ c/s. **This data superceded on page 21.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I A 2a. Aluminas (cont.)		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
Diamonite P-3530-40[a]	ϵ'/ϵ_o	8.95	8.95	8.95	8.95	8.95	8.95	8.95	8.95	8.90	8.85	8.77			
	tan δ	7.8	5.4	4.6	3	2	8	8	8	8.5	10.9	15			
Frenchtown 6096[b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	8.17					
	tan δ	----	----	----	----	----	----	----	----	13					
Frenchtown 7873[b,c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	6.60					
	tan δ	----	----	----	----	----	----	----	----	22					
General Ceramic ADH-211[d]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	7.93			
	tan δ	----	----	----	----	----	----	----	----	----	----	9.5			
Kearfott High Purity Alumina[e]	ϵ'/ϵ_o	9.40	9.40	9.40	9.40	----	----	----	----	----	----	9.40	9.40	----	9.4
	tan δ	3	< 2	< 2	< 5	----	----	----	----	----	----	1.8	1.5	----	1.7
"Sintox"[f]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	----	----	9.15	
	tan δ	----	----	----	----	----	----	----	----	----	----	----	----	16	
Norton 7x[g]	ϵ'/ϵ_o	9.65	9.64	9.64	9.64	9.64	9.64	9.64	----	----	----	9.63	9.62		
(density = 3.86 gm/cc)	tan δ	15.2	15.5	13.2	9	2.7	1.0	1.5	----	----	----	3.2	2.3		
Norton 17Z[g]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	9.20			
	tan δ	----	----	----	----	----	----	----	----	----	----	0.6			
Raytheon 402B[h]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	9.42			
	tan δ	----	----	----	----	----	----	----	----	----	----	14			
Stupakoff 1510[i,j]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	5.72			
	tan δ	----	----	----	----	----	----	----	----	----	----	16*			
Stupakoff 1540[i,k]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	8.97			
	tan δ	----	----	----	----	----	----	----	----	----	----	5.8			
Stupakoff 1542E[i,l]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	9.15			
	tan δ	----	----	----	----	----	----	----	----	----	----	6.8			
Stupakoff 1542P[i,m]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	9.34			
	tan δ	----	----	----	----	----	----	----	----	----	----	5.5			

a. Diamonite. b. Frenchtown. c. Alumina-mulite. d. Gen. Ceramics. e. Kearfott. f. Nat'l Res. Corp. g. Norton, experimental materials.

h. Raytheon. i. Stupakoff. j. 99.8% Al_2O_3, 10% porosity. k. 95% Al_2O_3, vitrified. l. 96% Al_2O_3, extruded. m. 96% Al_2O_3, pressed.

*At 50% relative humidity.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I A 2a. Aluminas (cont.)		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
Stupakoff 1550[a,b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	7.72			
	tan δ	----	----	----	----	----	----	----	----	----	----	16			
"Wesgo" AL-300[c,d]	ϵ'/ϵ_o	----	9.6	9.6	9.6	9.6	9.6	----	9.6	----	----	9.63			
	tan δ	----	8	2.5	1	1	0.7	----	1.6	----	----	5.5			
"Wesgo" AL-1009[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	7.03			
	tan δ	----	----	----	----	----	----	----	----	----	----	3.7			
I A 2b. Ferrites (Detailed data on other ferrites in ferromagnetics section). Values of tan δ are given without multiplying factor.															
Magnesium manganite[e]	ϵ'/ϵ_o	----	2710	869	98.3	24.6	18.4	15.5	----	12.1	11.2	10.9			
	tan δ	----	6.62	2.95	3.90	1.66	0.41	0.18	----	0.081	0.004	0.018			
"Ferramic" H-1[e]	ϵ'/ϵ_o	----	----	----	6940										
	$\tan\delta_d$	----	----	----	2.02	----	268	21.4							
	μ'/μ_o	----	680	672	660	570	268	21.4							
	$\tan\delta_m$	----	----	----	----	0.06	0.42	3.9							
"Ferroxcube" 105[f]	ϵ'/ϵ_o	----	----	----	----	----	11.9	----	11.2	11.0	11.0				
	$\tan\delta_d$	----	----	----	----	----	0.070	----	0.07	0.034	0.014				
	μ'/μ_o	----	----	----	----	----	----	----	----	3.53	0.57				
	$\tan\delta_m$	----	----	----	----	----	----	----	----	2.50	6.75				
I A 2c. Steatite	Values of tan δ are multiplied by 10^4; frequency given in c/s.														
Gen. Ceramics BN-3054	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	6.34			
	tan δ	----	----	----	----	----	----	----	----	----	----	18			
I A 2d. Wollastonites															
"AlSiMag" 577[g]	ϵ'/ϵ_o	6.54	6.54	6.54	6.54	6.54	6.54	6.53	6.52	----	----	6.45			
	tan δ	11	7.2	6.0	5.3	3.9	2.7	5.0	7.2	----	----	24			
Rutgers E-16[h]	ϵ'/ϵ_o	----	----	----	----	6.38	----	----	----	----	----	6.35	----	6.34	
(density = 2.85 gm/cc)	tan δ	----	----	----	----	1.9	----	----	----	----	----	12.5	----	17.0	

a. Stupakoff. b. 83% Al_2O_3, balance principally silica and calcium oxides. c. Western Gold and Platinum. d. 97% Al_2O_3, remainder mostly MgO.

e. Gen. Ceramics. f. Ferroxcube. g. Amer. Lava. h. Ceramics School, Rugers University.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I A 2e. Zircon		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
"AlSiMag" 475[a,b]	ϵ'/ϵ_o	9.07	8.66	8.57	8.5	8.5	8.5	8.5	8.5	----	----	8.35	7.51*	7.45*	
(density = 3.69 gm/cc)	tan δ	360	170	50	11	4.2	3.0	4.7	6.6	----	----	27	33	50	
I A 3. Glasses															
Corning 7910	ϵ'/ϵ_o	3.80	3.80	3.80	3.80	3.80	3.80	3.80	3.80	----	----	3.79			
Corning 8603:	tan δ	4.1	4.1	4.0	3.8	3.3	3.0	2.7	2.6	----	----	5.0			
"Fotoform" B (843GU)	ϵ'/ϵ_o	----	6.82	----	----	----	----	----	----	----	----	6.29	6.26	6.20	
	tan δ	----	186	----	----	----	----	----	----	----	----	137	149	195	
"Fotoform" B (843GZ)	ϵ'/ϵ_o	----	7.07	----	----	----	----	----	----	----	----	6.30	6.28	6.24	
	tan δ	----	257	----	----	----	----	----	----	----	----	147	177	246	
"Fotoform" C (843GU)	ϵ'/ϵ_o	----	5.95	----	----	----	----	----	----	----	----	5.64	5.62	5.59	
	tan δ	----	58	----	----	----	----	----	----	----	----	117	134	165	
"Fotoform" C (843GZ)	ϵ'/ϵ_o	----	6.01	----	----	----	----	----	----	----	----	5.71	5.70	5.69	
	tan δ	----	73	----	----	----	----	----	----	----	----	133	158	173	
"Fotoform" E (843GU)	ϵ'/ϵ_o	----	6.03	----	----	----	----	----	----	----	----	5.68	5.67	5.65	
	tan δ	----	43	----	----	----	----	----	----	----	----	104	139	160	
"Fotoform" E (843GZ)	ϵ'/ϵ_o	----	6.05	----	----	----	----	----	----	----	----	5.75	5.74	5.73	
	tan δ	----	73	----	----	----	----	----	----	----	----	123	160	168	
"Fotoceram" (843GU)	ϵ'/ϵ_o	----	5.62	----	----	----	----	----	----	----	----	5.45	5.44	5.43	
	tan δ	----	71	----	----	----	----	----	----	----	----	82	94	103	
"Fotoceram" (843GZ)	ϵ'/ϵ_o	----	5.63	----	----	----	----	----	----	----	----	5.46	5.45	5.44	
	tan δ	----	50	----	----	----	----	----	----	----	----	94	106	129	
"Ceram" 61-1[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	----	5.39		
	tan δ	----	----	----	----	----	----	----	----	----	----	----	4.5		
"Ceram" 61-2[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	----	5.38		
	tan δ	----	----	----	----	----	----	----	----	----	----	----	4.0		
"Ceram" 61-3[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	----	6.16		
	tan δ	----	----	----	----	----	----	----	----	----	----	----	4.0		

a. Amer. Lava. b. Zircon porcelain. c. Corning.
*Density = 3.43 gm./cc.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I A 3. Glasses (cont.)		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
"Ceram" 61-4[a]	ϵ'/ϵ_o	-----	----	----	----	----	----	----	----	----	----	----	6.14		
	tan δ	----	----	----	----	----	----	----	----	----	----	----	2.0		
"Ceram" 61-5[a]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	----	5.85		
	tan δ	----	----	----	----	----	----	----	----	----	----	----	2.5		
Owens-Corning CR-262[b]	ϵ'/ϵ_o	7.14	7.05	7.00	6.95	6.95	6.94	6.88	6.84	----	----	6.79			
	tan δ	95	70	55	46	42	40	47	55	----	----	130			
Owens-Corning 57M[b]	ϵ'/ϵ_o	6.52	6.50	6.50	6.48	6.50	6.49	6.46	6.44	----	----	6.42			
	tan δ	21	19	18	16	17	19	25	28	----	----	52			
Ownes-Corning EA63[b]	ϵ'/ϵ_o	7.26	7.16	7.12	7.10	7.09	7.06	7.00	6.98	----	----	6.92			
	tan δ	115	78	59	50	44	45	51	64	----	----	140			
Owens-Corning EA73[b]	ϵ'/ϵ_o	6.64	6.60	6.59	6.57	6.56	6.56	6.55	6.53	----	----	6.51			
	tan δ	30	21	18	15	14	18	23	28	----	----	57			
Owens-Corning X600[b]	ϵ'/ϵ_o	4.07	4.07	4.07	4.06	4.06	4.06	4.06	4.05	----	----	4.02			
	tan δ	7.4	5.8	4.0	4.0	4.8	6.8	9.3	11	----	----	17			
Fused Quartz, Clear[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	3.79			
	tan δ	----	----	----	----	----	----	----	----	----	----	1.1			
Fused Quartz, Translucent[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	3.65			
	tan δ	----	----	----	----	----	----	----	----	----	----	2.6			
I A 4. Miscellaneous Inorganics															
Boron nitride (dried, field ∥	ϵ'/ϵ_o	4.15	4.15	4.15	4.15	4.15	4.15	4.15	----	4.80*	4.80*	4.80*			
to direction of pressing)[d]	tan δ	----	----	----	----	----	----	----	----	0.57*	1.6*	3.1*			
"Fiberfrax" Board[d,e]	ϵ'/ϵ_o	4.81	2.45	1.91	1.75	1.67	1.64	1.62	1.60	1.74	1.64	1.61	1.6		
	tan δ	6500	4100	1180	400	170	140	170	250	460	470	250	360		
Silicon nitride (75%)	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	----	5.02*		
Boron nitride (25%)[d]	tan δ	----	----	----	----	----	----	----	----	----	----	----	300*		

a. Corning b. Research samples (Owens-Corning Fiberglas). c. Syncor. d. Hot-pressed (Carborundum). e. Aluminum-silicate ceramic fibers.
*Electric field ⊥ to direction of pressing.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I A 4. Miscellaneous Inorganics (cont.)

		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
"Eccofoam" HiK (1000°F)-2.5[a]	ϵ'/ϵ_o	----	2.62	----	----	----	----	----	----	----	----	2.49			
	tan δ_d	----	175	----	----	----	----	----	----	----	----	49			
	μ'/μ_o	----	----	----	----	----	----	----	----	----	----	0.992			
	tan δ_m	----	----	----	----	----	----	----	----	----	----	45			
"Eccofoam" HiK (1000°F)-3[a]	ϵ'/ϵ_o	----	3.02	----	----	----	----	----	----	----	----	3.08			
	tan δ_d	----	130	----	----	----	----	----	----	----	----	53			
	μ'/μ_o	----	----	----	----	----	----	----	----	----	----	0.960			
	tan δ_m	----	----	----	----	----	----	----	----	----	----	52			
"Eccofoam" HiK (1000°F)-5[a]	ϵ'/ϵ_o	----	5.48	----	----	----	----	----	----	----	----	5.35			
	tan δ_d	----	143	----	----	----	----	----	----	----	----	75			
	μ'/μ_o	----	----	----	----	----	----	----	----	----	----	0.961			
	tan δ_m	----	----	----	----	----	----	----	----	----	----	101			
Pipestone (50% R.H.)[b]	ϵ'/ϵ_o	40	13.9	8.93	6.86										
	tan δ	8400	2000	725	160										
Pipestone (baked, then paraffin impregnated)[b,c]	ϵ'/ϵ_o	5.15	5.10	5.07											
	tan δ	46	32	28											
"Supramica" 500[d] (density 3.04 gm/cc)	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	6.94			
	tan δ	----	----	----	----	----	----	----	----	----	----	24			
Sauereisen Cement No. 1 (after wet grinding)	ϵ'/ϵ_o	270	70	21	10.5	6.8	5.5	4.8							
	tan δ	86500	38600	19300	7800	2900	1100	620							
Sauereisen Cement No. 1 (after drying at 200°C)	ϵ'/ϵ_o	4.55	3.80	3.55	3.49	3.46	3.44	3.43	----	3.43	3.43				
	tan δ	3900	1300	400	190	82	60	56	----	54	54				
"Mica-ramic" (as received)[e]	ϵ'/ϵ_o	4.55	3.97	3.76	3.71	3.69	3.69	3.68							
	tan δ	1240	590	210	78	23	17	22							
"Mica-ramic" (after drying)[e]	ϵ'/ϵ_o	3.70	3.68	3.67	3.67	3.67	3.67	3.67							
	tan δ	69	46	33	23	17	15	15							

a. Emerson and Cuming. b. Hunson. c. Paraffin treated (Lab. Ins. Res.). d. Mycalex. e. Spruce Pine Mica.

I B. Solids, organic

1. Plastics (including plastics with fillers, laminates).

Values of tan δ are multiplied by 10^4; frequency given in c/s.

a. Phenolics		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
Phenolic impregnated "Dacron" batt[a]	ϵ'/ϵ_o	4.17	4.12	4.06	3.95	3.80	3.66	3.52	----	3.50	----	3.43			
	tan δ	103	100	157	231	270	271	-275	----	312	----	360			
Phenolic impregnated woven "Dacron" fabric[a]	ϵ'/ϵ_o	3.75	3.72	3.69	3.61	3.51	3.40	3.32	----	3.29	3.28	33.27			
	tan δ	59	66	114	167	190	202	240	----	280	280	230			
Phenolic impregnated "Nylon" batt[a]	ϵ'/ϵ_o	7.42	6.03	5.25	4.73	4.21	3.85	3.61	----	3.50	----	3.32			
	tan δ	1760	1060	922	900	708	517	440	----	364	----	377			
Phenolic impregnated woven "Nylon" fabric[a]	ϵ'/ϵ_o	3.99	3.88	3.78	3.68	3.56	3.45	3.35	3.30	3.24	3.20	3.13			
	tan δ	192	161	290	235	208	186	199	206	215	223	234			
Phenolic impregnated "Orlon" batt[a]	ϵ'/ϵ_o	4.75	4.54	4.35	4.18	4.05	3.90	3.74	----	3.62	----	3.47			
	tan δ	346	295	270	261	245	248	310	----	341	----	384			
Phenolic impregnated woven "Orlon" fabric[a]	ϵ'/ϵ_o	4.74	4.49	4.30	4.15	4.00	3.85	3.70	3.63	3.54	3.49	3.44			
	tan δ	440	325	264	243	218	212	244	245	257	268	327			
"Eccofoam" GL[b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	1.41			
	tan δ	----	----	----	----	----	----	----	----	----	----	115			
Phenolic-asbestos laminate, pressed (dried)[c]	ϵ'/ϵ_o	25.3	17.1	10.5	6.64	5.11	4.72	4.60	4.5	4.74*	----	4.57*	4.51*	4.47*	
	tan δ	2350	2880	3340	2610	1070	390	175	194	410*	----	390*	403*	435*	
Phenolic-"fiberglas" laminate laminate pressed (dried)[d]	ϵ'/ϵ_o	4.66	4.64	4.60	4.56	4.51	4.44	4.34	4.3	4.78*	4.76*	4.75*	4.74*	4.73*	
	tan δ	35	39	56	69	72	86	111	151	160*	190*	250*	280*	330*	
Phenolic-"fiberglas" laminate bagged (dried)[e]	ϵ'/ϵ_o	4.01	3.98	3.95	3.91	3.87	3.84	3.78	3.7	----	----	4.23*	4.23*	4.22*	
	tan δ	37	43	47	42	47	72	99	164	----	----	230*	215*	230*	

I B 1 b. Melamine-formaldehyde

"Dilecto" (Melamine glass laminate) GM-1, (dried)[f]	ϵ'/ϵ_o	4.69	4.62	4.60	4.59	4.59	4.57	4.52	----	3.98	3.95	3.91			
	tan δ	46	46	44	49	49	66	98	130	139	143	140			

a. du Pont Textile Fibers Dept. b. Emerson and Cuming. c. "Pyrotex 9526D2, 8 oz. mat (Raybestos Manhatten) with 34% Conolon 506 resin (Narmco) molded at 290°F, 200 psi and cured at temperatures to 400°F (Goodyear). d. 181-14 "Fiberglas" cloth with 31% resin as in (c), molded at 310°F, cured at 350°F (Goodyear). e. Composition same as (d) but with 3-ply bleeder. f. 50% Amer. Cyanamid 405 resin, 50% Owens-Corning T-36 glass mat (Continental Diamond).

*Sample not dried.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I B 1 c. Cellulose derivatives		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
"Forticel" JLB-(H)[a]	ϵ'/ϵ_o	3.59	3.57	3.51	3.41	3.29	3.18	3.08	----	2.97	2.93	2.89			
	tan δ	61	99	159	196	194	180	205	----	264	294	334			
"Forticel" JMB-(M)[a]	ϵ'/ϵ_o	3.94	3.89	3.82	3.70	3.55	3.41	3.25	----	3.06	2.97	2.88			
	tan δ	68	109	182	240	251	260	319	----	392	434	389			
"CTA"[b]	ϵ'/ϵ_o	4.11	3.99	3.86	3.67	3.51	3.38	3.23	----	3.07	3.01	2.92			
	tan δ	140	206	277	306	306	281	218	----	191	206	226			
I B 1 d. Silicon resins															
Silicone Alloy C-1147[c]	ϵ'/ϵ_o	----	----	----	----	2.52	2.52	2.52	2.52	2.51	2.50	2.49	2.48	2.48	2.48
	tan δ	----	----	----	----	0.6	2.5	3.3	4.0	5.0	6.0	7.1	8.1	9.0	14.2
Silicone Alloy C-1328[c]	ϵ'/ϵ_o	----	----	----	----	2.50	2.50	2.50	2.49	2.49	2.48	2.48	2.48	2.48	2.48
	tan δ	----	----	----	----	1.2	3.4	2.2	1.9	2.8	3.2	4.0	4.4	4.8	5.9
DC 301 molding compound[d]	ϵ'/ϵ_o	4.16	4.12	4.10	4.08	4.07	4.06	4.04							
	tan δ	63	63	53	49	50	51	67							
DC 2105 laminate[e]	ϵ'/ϵ_o	3.98	3.98	3.97	3.96	3.96	3.96	3.96	----	4.18	4.17	4.16			
	tan δ	19.3	18.6	15.9	15	14.4	16.6	25	----	58	61	69			
DC 2106 laminate[f]	ϵ'/ϵ_o	4.24	4.24	4.22	4.22	4.21	4.21	4.21	----	4.32	4.31	4.30			
	tan δ	23	18.2	15.2	12	14	17	23	----	45	52	66			
Silicone - asbestos laminate[g]	ϵ'/ϵ_o	12.80	9.90	6.65	4.59	3.68	3.45	3.39	3.3	3.68*	3.58*	3.52*	3.49*	3.49*	
	tan δ	1870	2400	2650	2090	1020	460	50	45	500*	340*	210*	190*	130*	
Silicone - "fiberglas" laminate, pressed (dried)[h]	ϵ'/ϵ_o	3.66	3.63	3.61	3.60	3.59	3.58	3.56	3.5	3.91*	3.88*	3.85*	3.83*	3.81*	
	tan δ	10.7	9.8	8.7	9.4	10.0	12.2	19	26	33*	43*	65*	75*	113*	
Silicone - "fiberglas" laminate, bagged (dried)[i]	ϵ'/ϵ_o	3.13	3.13	3.13	3.13	3.13	3.13	3.13	3.1	----	3.84*	3.80*	3.78*	3.75*	
	tan δ	21.3	16.7	15.4	14	13.2	13.1	19.3	24	----	56*	70*	88*	110*	

a. Cellulose propionate (Celanese). b. Cellulose tri-acetate (du Pont Film Dept.). c. Delaware Res. Dev. d. 45% chopped glass fibers, 20% silica, 35% polysiloxane resin (Dow-Corning). e. 50% EC-116 glass fabric, 50% polysiloxane resin (Dow-Corning). f. 70% ECC-181 glass fabric, 30% polysiloxane resin (Dow-Corning). g. 50% "Pyrotex" felt 9526DB-5, impregnated with 50% DC-2106 resin (U. S. Polymeric), molded at 350°F, 300 psi, and cured at temperatures to 470°F (Goodyear). h. 65% 181-112 cloth, 35% DC-2106 resin molded at 315°F, cured at temperatures to 480°F (Goodyear).
i. Composition same as (a), but with 3-ply bleeder, 33% resin.

*Not dried.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I B 1 e. Polyvinyl resins

		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
(1). Polyethylenes															
"Fortiflex" A[a]	ϵ'/ϵ_o	2.39	2.38	2.38	2.38	2.38	2.38	2.38	----	2.38	2.38	2.37			
	tan δ	1.1	0.37	0.25	<0.5	<0.3	<0.3	0.3	----	3.1	2.6	1.9			
"Marlex" 50[b]	ϵ'/ϵ_o	2.40	2.40	2.40	2.40	2.40	2.40	2.40	2.40	2.39	2.39	2.38	2.38	2.38	
	tan δ	1.6	0.33	0.28	<0.5	0.28	<0.3	0.32	0.9	2.4	2.15	1.6	1.9	2.1	
(2). Polyvinyl chloride-acetate															
"Boltaron" 6200-10[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	2.81					
	tan δ	----	----	----	----	----	----	----	----	82					
(3). Polychlorotrifluoroethylene															
"KEL-F" X200[d]	ϵ'/ϵ_o	3.13	3.00	2.84	2.70	2.56	2.45	2.36	----	2.30	2.28	2.27			
	tan δ	198	292	398	420	320	220	180	----	96	73	56			
(4). Polytetrafluoroethylene															
"Teflon" (77%) plus	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	2.38					
calcium fluoride (23%)[e]	tan δ	----	----	----	----	----	----	----	----	57					
(5). Polyacrylates															
"Lucite" Type HC-202[f]	ϵ'/ϵ_o	3.27	3.01	2.87	2.76	2.71	2.66	2.63	----	2.58	2.56	2.55			
	tan δ	590	446	300	202	142	90	63	----	43	37	33			
Acrylic impregnated	ϵ'/ϵ_o	3.76	3.47	3.25	3.10	2.98	2.91	2.84	----	2.77	2.74	2.72			
Orlon batt[g]	tan δ	664	503	362	277	213	168	118	----	86	72	59			
(6). Polystyrene															
Polystyrene impregnated	ϵ'/ϵ_o	3.11	3.10	3.10	3.10	3.10	3.10	3.10	---	3.16	3.16	3.16			
"Fiberglas" g	tan δ	55	24.6	18.2	15.6	4.6	6.1	11.3	----	28	39	36			
Polystyrene impregnated	ϵ'/ϵ_o	3.02	3.01	3.00	3.00	3.00	2.97	2.91	----	2.87	2.84	2.82			
"Dacron" batt[g]	tan δ	43	30	32.6	46	60	79	78	----	113	130	157			
Polystyrene impregnated	ϵ'/ϵ_o	3.09	2.98	2.92	2.89	2.87	2.86	2.85	----	2.89	2.88	2.87			
"Orlon" batt[g]	tan δ	211	159	113	78	45	33	26	----	26	28	36			
"Eccofoam" PS (K=1.2)[h]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	1.182			
	tan δ	----	----	----	----	----	----	----	----	----	----	1.2			

a. Linear polyethylene (Celanese). b. Low pressure, hi-density polyethylene (Phillips). c. 100% unplasticized polyvinyl chloride (Hartwell). d. Kellogg. e. Ethylene Chem. f. Methyl methacrylate (du Pont Polychemicals). g. du Pont Textile Fibers Dept. h. Samples also measured having $\epsilon'/\epsilon_o = 1.362$, tan δ = 0.00032; and $\epsilon'/\epsilon_o = 2.05$, tan δ = 0.00165 (Emerson & Cuming).

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I B 1 e. Polystyrene (cont.)															
(7). Miscellaneous polystyrenes		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
Polytrifluorostyrene (film)[a]	ϵ'/ϵ_o	2.56	2.56	2.56	2.56	2.56	2.56	2.56	----	----	----	2.54			
	tan δ	34	27	16.5	14	6.2	6.3	6.9	----	----	----	19			
Polycyclostyrene[b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	2.51	2.49			
	tan δ	----	----	----	----	----	----	----	----	----	--31	26			
(8). Styrene copolymers, cross linked															
"Pelron" 9420[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	2.59	2.54				
	tan δ	----	----	----	----	----	----	----	----	22	29				
"Pelron" 9422[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	2.61	2.61				
	tan δ	----	----	----	----	----	----	----	----	44	51				
"Pelron" 9423[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	2.62	2.61				
	tan δ	----	----	----	----	----	----	----	----	50	59				
"Pelron" 9424[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	2.60	2.60				
	tan δ	----	----	----	----	----	----	----	----	30	39				
"Ecco" L65[d]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	2.58	2.58				
	tan δ	----	----	----	----	----	----	----	----	30	34				
"Stycast" LoK[d]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----			1.68			
	tan δ	----	----	----	----	----	----	----	----	----	----	26			
"Stycast" HiK (K=7)[d,e]	ϵ'/ϵ_o	7.25	7.15	7.08	7.06	----	7.03	----	----	----	----	6.85			
	tan δ	99	61	36	23	----	9.5	----	----	----	----	11			
"Stycast" TPM-3[d]	ϵ'/ϵ_o	2.40	2.40	2.40	2.40	2.39	2.37	2.36	----	----	----	2.35			
	tan δ	2.9	1.7	1.9	2.8	7.3	7.2	5.8	----	----	----	4.6			
"Rexolite" 2101[h]	ϵ'/ϵ_o	2.73	2.73	2.73	2.73	2.73	2.73	2.73	2.72	----	----	2.75			
	tan δ	13.5	9.6	7.5	5	4	6.5	10	12	----	----	19			
I B 1 f. Polyesters															
"Atlac" 382 (70%)-styrene (30%)[i]	ϵ'/ϵ_o	3.08	3.05	3.02	3.00	2.96	2.92	2.87	----	2.82	2.78	2.72			
	tan δ	85	75	70	80	110	132	142	----	135	120	105			

a. Polaroid. b. Monsanto, Ohio. c. East Coast Aeronautics. d. Emerson and Cuming. e. Manufactured with K=3 to 15. h. "Fiberglas" laminate (Rex). i. Atlas Powder.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I B 1 f. Polyesters (cont.)		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
"Atlac" 382 (50%) - styrene (50%)[a]	ϵ'/ϵ_o	2.91	2.90	2.89	2.87	2.84	2.82	2.77	----	2.72	2.69	2.65			
	tan δ	42	44	44	54	73	90	115	----	108	95	75			
"Bakelite" PLLA-5005[b]	ϵ'/ϵ_o	2.22	2.05	1.97	1.90	1.84	1.78	1.73	----	1.69	1.67	1.65			
	tan δ	1006	396	255	218	200	210	240	----	235	200	200			
"Dilecto" (glass mat polyester) GM-PE (dried)[c]	ϵ'/ϵ_o	4.65	4.57	4.53	4.50	4.45	4.43	4.40	----	4.40	4.35	4.30			
	tan δ	48	45	41	63	77	96	120	----	95	102	106			
Celanese MR-31C	ϵ'/ϵ_o	3.43	3.40	3.36	3.32	3.26	3.17	3.11	----	2.97	2.93	2.86			
	tan δ	65	61	78	125	148	143	160	----	147	124	114			
Celanese MR-33C	ϵ'/ϵ_o	3.11	3.06	3.06	3.02	2.98	2.97	2.94	----	2.91	2.89	2.82			
	tan δ	22	27	46	79	82	87	128	----	145	130	129			
Celanese MX-186	ϵ'/ϵ_o	5.55	5.26	4.98	4.70	4.42	4.15	3.86	----	3.55	3.42	3.28			
	tan δ	360	360	370	370	370	500	600	----	570	470	380			
Celanese MX-218	ϵ'/ϵ_o	3.91	3.81	3.71	3.63	3.56	3.47	3.33	----	----	----	----	2.96	2.94	
	tan δ	202	172	162	162	161	195	320	----	----	----	----	410	288	
Polyester impregnated "Dacron" batt[d]	ϵ'/ϵ_o	3.37	3.35	3.32	3.28	3.20	3.13	3.05	3.03	3.00	2.99	2.98			
	tan δ	48	51	86	152	182	179	143	123	98	81	68			
Polyester impregnated "Dacron" batt[e]	ϵ'/ϵ_o	3.61	3.53	3.47	3.37	3.26	3.15	3.07	----	3.03	3.02	3.01			
	tan δ	119	111	135	185	226	223	205	----	144	105	113			
Polyester impregnated woven "Dacron" fabric[d]	ϵ'/ϵ_o	2.99	2.96	2.89	2.86	2.83	2.77	2.71	----	2.74	----	2.65			
	tan δ	39	47	80	127	152	152	137	----	92	----	93			
Polyester impregnated "Nylon" batt[d]	ϵ'/ϵ_o	3.84	3.72	3.59	3.45	3.32	3.22	3.09	3.05	3.00	2.96	2.91			
	tan δ	309	239	255	283	261	185	137	126	113	105	97			
Polyester impregnated woven "Nylon" fabric[d]	ϵ'/ϵ_o	3.16	3.12	3.04	2.93	2.86	2.77	2.54	----	2.92	----	2.89			
	tan δ	133	146	196	233	228	197	167	----	84	----	76			
Polyester impregnated "Orlon" batt[d]	ϵ'/ϵ_o	3.72	3.61	3.50	3.40	3.31	3.24	3.18	3.15	3.13	3.11	3.08			
	tan δ	277	200	184	187	186	170	139	120	100	92	89			
Polyester impregnated woven "Orlon" fabric[d]	ϵ'/ϵ_o	4.08	3.90	3.78	3.68	3.60	3.51	3.39							
	tan δ	337	258	201	179	160	141	125							

a. Atlas Powder. b. Phenolic spheres in polyester resin (Bakelite). c. Continental Diamond. d. Rohm and Haas', "Paraplex" P-43 resin (du Pont Textile Fibers Dept.) e. Robertson's "Stypol" 16D resin (du Pont Textile Fibers Dept.).

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I B 1 f. Polyesters (cont.)		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
"Mylar" A[a] electric field	ϵ'/ϵ_o	3.17	3.15	3.13	3.07	2.99	2.92	2.87	----	2.81	2.79	3.19*			
to film	tan δ	19.1	41.0	89.9	145	166	160	130	----	76	61	44*			
"Cronar"[b]	ϵ'/ϵ_o	3.37	3.36	3.33	3.29	3.23	3.17	3.10	----	3.01	2.96	2.90			
	tan δ	15	36	84	140	175	170	150	----	120	105	82			
"Eccosorb" HF155[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	17.8			
	tan δ	----	----	----	----	----	----	----	----	----	----	3700			
"Eccosorb" HF680[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	23.2			
	tan δ	----	----	----	----	----	----	----	----	----	----	2700			
"Eccosorb" HF853[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	19.5			
	tan δ	----	----	----	----	----	----	----	----	----	----	2700			
"Eccosorb" HF1000[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	12.8			
	tan δ	----	----	----	----	----	----	----	----	----	----	1600			
"Eccosorb" HF2050[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	9.1			
	tan δ	----	----	----	----	----	----	----	----	----	----	1500			
"Eccosorb" HFX122[c,d]	ϵ'/ϵ_o	----	----	23,000	23,000	6200	1070	----	----	----	----	42			
	tan δ	----	----	330*	33*	12*	7*	----	----	----	----	5300			
"Eccosorb" HFX123[c,e]	ϵ'/ϵ_o	----	----	20,400	16,000	2400	1070	----	----	----	----	22			
	tan δ	----	----	304*	38*	24*	5.8*	----	----	----	----	8900			
Hooker 32A, "Fiberglas"	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	3.70	3.68	3.67			
cloth laminate[f]	tan δ	----	----	----	----	----	----	----	----	135	141	128			
Hooker 32A, "Fiberglas"	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	3.68	3.63	3.62			
mat[g]	tan δ	----	----	----	----	----	----	----	----	141	148	168			
Hooker 32A, "Fiberglas"	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	3.78	3.75	3.73			
mat with fire retardent[h]	tan δ	----	----	----	----	----	----	----	----	118	143	143			
"Selectron" 5084[i]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	2.89			
	tan δ	----	----	----	----	----	----	----	----	----	----	155			

a. du Pont Film Dept. b. du Pont Photo Products Dept. c. Emerson and Cuming. d. 43.6% Graphite, 56.4% resin. e. 16.2% Acetylene black, 83.8% resin. f. Chlorinated polyester resin, 2% ATC catalyst, with 50% Owens-Corning 181 Volan cloth (Hooker). g. Same resin with 45% Owens-Corning OCF T219 glass mat (Hooker). h. Same as g but with 5% Sb_2O_3 added to resin (Hooker). i. Pittsburg Corning.

*Electric field ||. **tan δ not multiplied by 10^4.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I B 1 g. Epoxy resins		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
"Dilecto" (Epoxy-glass laminate)	ϵ'/ϵ_o	5.20	5.16	5.10	4.99	4.90	4.76	4.66	4.82	4.75	4.67	4.64			
GB-116E[a]	tan δ	46	72	118	176	185	205	233	162	170	176	213			
"Dilecto" (Epoxy-glass laminate)	ϵ'/ϵ_o	5.25	5.21	5.12	5.00	4.91	4.75	4.63	4.65	4.54	4.48	4.42			
GB-126E[a]	tan δ	60	74	136	190	192	202	223	175	186	182	210			
"Dilecto" (Epoxy-glass laminate)	ϵ'/ϵ_o	5.25	5.21	5.14	5.03	4.90	4.77	4.65	4.85	4.80	4.73	4.64			
GB-181E[a]	tan δ	42	67	131	178	204	226	268	165	179	202	218			
Epoxy impregnated	ϵ'/ϵ_o	4.12	4.08	4.00	4.84	3.66	3.49	3.37	----	3.25	3.21	3.16			
"Dacron" batt[b]	tan δ	49	107	208	277	290	300	300	----	270	260	240			
Epoxy impregnated	ϵ'/ϵ_o	3.71	3.69	3.66	3.59	3.49	3.39	3.30	----	3.18	3.15	3.12			
woven "Dacron" fabric[b]	tan δ	32	51	102	158	194	248	256	----	310	300	250			
Epoxy impregnated	ϵ'/ϵ_o	4.62	4.48	4.28	4.03	3.78	3.64	3.45	----	3.24	----	3.06			
"Nylon" batt[b]	tan δ	189	253	369	407	336	323	330	----	320	----	280			
Epoxy impregnated	ϵ'/ϵ_o	4.34	4.26	4.11	3.91	3.72	3.61	3.53	----	3.33	3.25	3.12			
woven "Nylon" fabric[b]	tan δ	125	183	285	334	304	314	343	----	320	310	270			
Epoxy impregnated	ϵ'/ϵ_o	4.42	4.23	4.07	3.93	3.81	3.69	3.54	----	3.32	----	3.15			
"Orlon" batt[b]	tan δ	332	284	257	235	203	233	268	----	204	----	181			
Epoxy impregnated	ϵ'/ϵ_o	4.35	4.18	4.02	3.89	3.76	3.68	3.57	----	3.45	3.38	3.32			
woven "Orlon" fabric[b]	tan δ	304	251	236	229	215	237	310	----	310	300	280			
"Eccofoam" HiK (500°F)	$\epsilon'/\epsilon_o \cdot \mu'/\mu_o$	----	----	----	----	----	----	----	----	----	----	2.41			
(K = 2.4)[c]	$\tan\delta_d + \tan\delta_m$	----	----	----	----	----	----	----	----	----	----	160			
"Eccofoam" HiK (500°F)	$\epsilon'/\epsilon_o \cdot \mu'/\mu_o$	----	----	----	----	----	----	----	----	----	----	4.53			
(K = 4.5)[c]	$\tan\delta_d + \tan\delta_m$	----	----	----	----	----	----	----	----	----	----	270			
"Eccofoam" HiK (500°F)	$\epsilon'/\epsilon_o \cdot \mu'/\mu_o$	----	----	----	----	----	----	----	----	----	----	5.85			
(K = 5.9)[c]	$\tan\delta_d + \tan\delta_m$	----	----	----	----	----	----	----	----	----	----	460			
"Eccofoam" HiK (500°F)	$\epsilon'/\epsilon_o \cdot \mu'/\mu_o$	----	----	----	----	----	----	----	----	----	----	7.54			
(K = 7.5)[c]	$\tan\delta + \tan\delta_m$	----	----	----	----	----	----	----	----	----	----	460			

a. Continental Diamond. b. du Pont Textile Fibers Dept. c. Emerson and Cuming.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I B 1g. Epoxy resins (cont.)		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
"Eccosorb" MF110[a]	ϵ'/ϵ_o	----	----	5.38	5.18	----	----	----	----	----	----	3.95			
	tan δ_d	----	----	161	234	----	----	----	----	----	----	326			
	μ'/μ_o	----	----	1.33	1.33	----	----	----	----	----	----	1.115			
	tan δ_m	----	----	----	----	----	----	----	----	----	----	880			
"Eccosorb" MF112[a]	ϵ'/ϵ_o	----	----	6.72	6.55	----	----	----	----	----	----	5.00			
	tan δ_d	----	----	162	247	----	----	----	----	----	----	334			
	μ'/μ_o	----	----	1.67	1.67	----	----	----	----	----	----	1.40			
	tan δ_m	----	----	----	----	----	----	----	----	----	----	1890			
"Eccosorb" MF114[a]	ϵ'/ϵ_o	----	----	11.2	10.8	----	----	----	----	----	----	8.60			
	tan δ_d	----	----	181	255	----	----	----	----	----	----	338			
	μ'/μ_o	----	----	2.64	2.64	----	----	----	----	----	----	1.66			
	tan δ_m	----	----	----	----	----	----	----	----	----	----	3900			
"Eccosorb" MF116[a,b]	ϵ'/ϵ_o	19.9	19.6	19.2	18.5	18.1	17.1	16.9	----	----	----	13.6			
	tan δ_d	134	128	177	228	254	307	394	----	----	----	220			
	μ'/μ_o	4.22	4.22	4.22	4.22	4.22	4.22	4.20	3.90	3.75	2.34	1.12			
	tan δ_m	----	----	----	----	<100	<100	<200	570	2650	4820	6000			
"Eccosorb" MF117[a,c]	ϵ'/ϵ_o	24.2	23.9	23.2	----	21.4	19.9	19.6	----	----	----	17.2			
	tan δ_d	94	144	250	----	360	390	420	----	----	----	380			
	μ'/μ_o	4.85	4.85	4.85	4.85	4.85	4.85	4.80	4.69	4.31	2.57	1.96			
	tan δ_m	----	----	----	----	<100	<50	<200	560	2950	5600	7300			
"Hysol" 6000 HD[d]	ϵ'/ϵ_o	3.22	3.21	3.19	3.15	3.10	3.01	2.90	----	2.84	2.82	2.81			
	tan δ	34	44	74	108	133	146	180	----	132	120	116			
"Hysol" 6030-B[d]	ϵ'/ϵ_o	9.7	9.4	8.9	8.1	7.3	5.8	4.3	----	3.30	3.27	----			
	tan δ	5600	1160	670	540	1000	2300	1100	----	635	660	-----			
"Hysol" XL-6060[d]	ϵ'/ϵ_o	8.80	7.56	6.45	5.60	4.90	4.35	3.70	----	3.40	3.23	3.10			
	tan δ	2500	1450	1040	840	960	1140	1150	----	670	570	370			

a. Emerson and Cuming. b. 81.2% Carbonyl iron, 18.8% resin. c. 85.8% Carbonyl iron, 14.2% resin. d. Houghton Labs.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
I B 1 g. Epoxy resins (cont.)															
"Hysol" XE-6080[a]	ϵ'/ϵ_o	3.70	3.55	3.42	3.34	3.28	3.20	3.06	----	2.86	2.83	2.81			
	tan δ	77	69	80	126	194	280	270	----	215	194	195			
"Scotchply" type 1001[b]	ϵ'/ϵ_o	6.60	5.98	5.59	5.32	5.10	4.89	4.71	----	4.59	4.48	4.38			
(molded, uncured)	tan δ	571	458	342	207	219	288	384	----	450	470	460			
"Scotchply" type 1001[b]	ϵ'/ϵ_o	5.18	5.12	5.02	4.92	4.82	4.68	4.57	----	4.56	4.56	4.56			
(cured)	tan δ	78	97	139	166	184	199	194	----	178	168	152			
"Epon" 828-curing agent CL[c]	ϵ'/ϵ_o	4.56	4.48	4.34	4.12	3.91	3.72	3.55	----	3.29	3.23	3.23			
	tan δ	61	150	290	370	340	340	360	----	310	310	330			
"Epon" 828-curing agent D[c]	ϵ'/ϵ_o	3.58	3.55	3.52	3.47	3.36	3.27	3.18	----	3.03					
	tan δ	27	45	88	170	230	270	240	----	250					
"Epon" 828-curing agent	ϵ'/ϵ_o	3.61	3.61	3.59	3.56	3.47	3.38	3.27	----	2.94					
piperidine[c]	tan δ	18	23	56	130	180	220	260	----	270					
"Epon" 828-curing agent	ϵ'/ϵ_o	3.84	3.84	3.79	3.68	3.51	3.37	3.30	3.14	3.05	3.00	2.97	2.94	2.93	
BF_3-400[c]	tan δ	44	64	135	257	312	305	280	250	222	202	203	210	186	
"Epon" 828 "fiberglas" laminate,	ϵ'/ϵ_o	4.82	4.79	4.74	4.68	4.60	4.47	4.32	----	4.34	4.28	4.25	4.22	4.21	
curing agent BF_3-400[c,d]	tan δ	46	41	69	124	171	182	168	----	135	131	131	148	192	
"Epon" X131 "fiberglas"	ϵ'/ϵ_o	5.46	5.42	5.38	5.27	5.24	5.06	4.84	----						
laminate, No. 51[c]	tan δ	39	40	62	124	184	246	304							
I B 1 h. Miscellaneous plastics															
"Penton"[e]	ϵ'/ϵ_o	3.03	2.99	2.95	2.92	2.88	2.85	2.81	----	2.73	2.70	2.63			
	tan δ	112	98	85	79	98	124	170	----	196	155	112			
"Policap"[f]	ϵ'/ϵ_o	4.12	3.80	3.40	3.05	2.88	2.82	2.80	----	2.75	2.75	2.75			
	tan δ	444	666	748	513	233	107	71.5	----	62.0	60	52			
I B 2. Waxes															
Morse 200	ϵ'/ϵ_o	2.34	2.34	2.34	2.34	2.34	2.3								
	tan δ	9.1	7.6	7.0	5.9	10	10								

a. Houghton Labs. b. "Fiberglas" laminate (Minn. Mining). c. Shell. d. 181-"Volan" A cloth pressed at 125°C, cured at 330°F, 200 psi, post-cured 4 hours at 200°C; resin content 23.8%. e. Chlorinated polyether (Hercules). f. Lovell.

Values of tan δ are multiplied by 10^4; frequency given in cδs.

I B 2. Waxes (cont.)		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$	$1.4x10^{10}$	$2.4x10^{10}$	$5x10^{10}$
Morse 280	ϵ'/ϵ_o	3.30	3.03	2.71	2.53	2.48	2.48								
	tan δ	620	690	660	290	66	29								
Morse 300	ϵ'/ϵ_o	3.74	3.07	2.71	2.64	2.61	2.60								
	tan δ	1810	1030	490	189	83	46								
Morse 400	ϵ'/ϵ_o	2.88	2.74	2.68	2.62	2.58	2.52								
	tan δ	474	267	136	103	152	87								
Morse 6060-C	ϵ'/ϵ_o	2.18	2.17	2.15	2.14	2.11	2.11								
	tan δ	52	56	41	20	7	3								
Morse 6062	ϵ'/ϵ_o	2.31	2.31	2.31	2.31	2.28	2.25								
	tan δ	13.5	10	11	10	11	9								
I B 3. Miscellaneous organics															
"Missileon"[a]	ϵ'/ϵ_o	6.00	5.14	4.69	4.43	4.25	4.08	3.98	----	----	----	3.88			
	tan δ	1410	870	500	330	280	260	260	----	----	----	560			
"Rocketon"[a]	ϵ'/ϵ_o	7.66	5.88	5.02	4.58	4.29	4.11	3.99	----	----	----	3.95			
	tan δ	2280	1500	860	540	360	320	350	----	----	----	440			
"Rocketon" (Modification 30)[a]	ϵ'/ϵ_o	4.46	4.13	3.97	3.86	3.80	3.73	3.68	----	----	----	3.59			
	tan δ	774	430	223	163	125	124	142	----	----	----	220			
Irvington varnished linen tape	ϵ'/ϵ_o	----	----	----	4.22	----	2.58								
	tan δ	----	----	----	513	----	560								
"Scotch" tape No. 39[b]	ϵ'/ϵ_o	----	----	----	----	----	3.34 (at $3x10^7$)								
	tan δ	----	----	----	----	----	390 (at $3x10^7$)								
Sealing Compound EC-612[b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	17.4				
	tan δ	----	----	----	----	-----	----	----	----	----	1140				
"Ferrotron" 119 (core)[c]	ϵ'/ϵ_o	31.8	29.1	27.9	27.2	26.8	26.3	25.2	----	24	24	24	20		
	tan δ_d	1130	460	230	160	130	144	150	----	<200	<200	<1500	<1000		
	μ'/μ_o	----	7.10	7.10	7.10	7.10	6.99	6.2	----	6.28	4.60	1.96	0.98		
	tan δ_m	----	----	----	----	10	20	65	----	3000	6700	14,500	20,600		

a. Haveg. b. Minnesota Mining. c. Polymer Corp.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I B 3. Miscellaneous organics (cont.)		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
"Ferrotron" 308 (rod)[a]	ϵ'/ϵ_o	16.5	15.5	15.3	15.2	15.0	14.8	----	----	----	----	8.0*	----	6.3	
	tan δ_d	460	300	130	90	86	80	----	----	----	----	130*	----	150	
	μ'/μ_o	----	4.7	4.7	4.7	4.7	4.7	3.6	----	3.4	----	1.19	----	0.84	
	tan δ_m	----	----	----	----	20	80	300	----	2400	----	8900*	----	8400	
"Ferrotron" 309 (tape)[a]	ϵ'/ϵ_o	15.8	15.5	15.5	15.1	15.1	15	15	----	15	15	15	----	11	
	tan δ_d	380	250	108	58	34	29	61	----	120	<500	<1000	----	140	
	μ'/μ_o	----	----	----	----	5.54	5.65	5.4	----	4.93	3.56	1.60	----	0.44	
	tan δ_m	----	----	----	----	< 20	<200	350	----	3000	5300	12,900	----	24,000	
Varnish impregnated Kraft paper[b]	ϵ'/ϵ_o	----	4.5	----	----	4.0									
	tan δ	----	300	----	----	300									
Varnished glass cloth[c]	ϵ'/ϵ_o	----	3.9	----	----	3.5									
	tan δ	----	360	----	----	250									
Silicone varnished glass cloth, flexible[c,d]	ϵ'/ϵ_o	----	3.3	----	----	3.2									
	tan δ	----	82	----	----	28									
Silicone varnished glass cloth, stiff[c,d]	ϵ'/ϵ_o	----	2.8	----	----	2.8									
	tan δ	----	42	----	----	14									
I C. Liquids															
1. Inorganic															
Nitrogen -195°[e]	ϵ'/ϵ_o	----	1.45												
	tan δ	----	<2												
2. Organic															
a. Aliphatic															
"Kel-F" Alkane 464[f]	ϵ'/ϵ_o	2.55	2.55	2.55	2.55	2.55	2.55	2.55	2.54	2.54	2.51	2.30*			
	tan δ	1.4	0.2	<0.3	<0.3	<0.3	1.3	14	44	150	420	930*			
"Kel-F" Alkane 695[g]	ϵ'/ϵ_o	2.69	2.69	2.69	2.69	2.69	2.69	2.68	2.65	2.63	2.50	2.26*			
	tan δ	2.2	0.2	<0.3	< 1	0.7	7	70	190	470	870	890*			

a. Polymer Corp. b. ASTM type A paper (D 1305), vacuum-impregnated with Sterling M50 (Sperry test sample). c. Sperry test sample.
d. R-63 varnish (Union Carbide and Carbon). e. Cryogenic Eng. Lab, M. I. T. f. Chlorotrifluoroethylene dimer (Kellogg). g. Ibid., trimer.
*Freq = 9.5×10^9

Values of tan δ are multiplied by 10^4; frequency given in c/s.

I C. Liquids (cont.)

2. Organic a. Aliphatic		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
"KEL-F" Alkane 8126[a]	ϵ'/ϵ_o	2.88	2.88	2.88	2.88	2.88	2.88	2.87	2.80	2.61	2.37	2.16			
	tan δ	1.5	0.15	<0.1	<0.4	2.8	28	275	650	1080	990	684			
"KEL-F" Alkane 10157[b]	ϵ'/ϵ_o	2.88	2.88	2.88	2.88	2.88	2.88	2.70	----	2.39	2.28	2.23			
	tan δ	<0.2	<0.1	0.1	1.0	9.6	96	710	----	780	480	335			
"KEL-F" Alkane 12188[c]	ϵ'/ϵ_o	2.94	2.94	2.94	2.94	2.94	2.90	----	----	2.33	2.24	2.23			
	tan δ	<0.2	<0.1	0.6	5.7	55	550	----	----	485	330	218			
Hexane[d]	ϵ'/ϵ_o	----	----	1.84											
	tan δ	----	----	< 1											
b. Aromatic															
OS-45[e]	ϵ'/ϵ_o	2.65	2.65	2.65	2.65	2.65	2.64	2.63	----	2.48					
	tan δ	3400	336	34	21	42	41	130	----	482					
OS-59, tetra alkyl silicate	ϵ'/ϵ_o	2.46	2.46	2.46	2.46	2.46	2.46	2.46	----	2.41	2.33	2.24			
ester[e]	tan δ	12.4	1.3	0.2	<0.3	<0.6	5	50	----	324	410	380			
OS-82, monoisopropyl biphenyl[e]	ϵ'/ϵ_o	2.61	2.61	2.61	2.61	2.61	2.61	2.60	2.57	2.52	2.51				
	tan δ	150	15	1.5	<0.6	1	12	115	220	183	100				
Diisopropyl biphenyl[e]	ϵ'/ϵ_o	2.54	2.54	2.54	2.54	2.54	2.54	2.53	2.49	2.44	2.41				
	tan δ	6	0.6	0.2	<0.4	1.9	19	135	190	120	66				
"Selectron" 5084 monomer[f]	ϵ'/ϵ_o	----	----	----	----	----	----	----		----	----	3.01			
	tan δ	----	----	----	----	----	----	----		----	----	410			
"Stypol" 16B monomer[g]	ϵ'/ϵ_o	----	----	7.16	----	----	----	----	----	----	----	3.02			
	tan δ	----	----	79	----	----	----	----	----	----	----	420			
c. Petroleum oil															
Jet fuel JP-4	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	2.04*			
	tan δ	----	----	----	----	----	----	----	----	----	----	30*			

a. Chlorotrifluoroethylene tetrameter. b. Ibid., pentamer. c. Ibid., hexamer. d. Phillips. e. Monsanto (St. Louis). f. Pittsburg-Corning.
g. Robertson.

*Freq = 9.5×10^9.

Values of tan δ are multiplied by 10^4; frequency given in c/s.

		1×10^2	1×10^3	1×10^4	1×10^5	1×10^6	1×10^7	1×10^8	3×10^8	1×10^9	3×10^9	8.6×10^9	1.4×10^{10}	2.4×10^{10}	5×10^{10}
I C 2 d. Silicones															
High Vacuum Grease[a]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	2.80	2.74			
	tan δ	----	----	----	----	----	----	----	----	----	80	200			
DC XF-6620[a]	ϵ'/ϵ_o	2.81	2.81	2.81	2.81	2.81	2.81	2.81	2.80	2.79	2.67	2.41			
	tan δ	3	0.3	<0.1	<0.1	<0.2	1.7	17	48	103	180	217			
I D. Gases															
Nitrogen 14.7 psi[b]	ϵ'/ϵ_o	----	----1.00058		----	----	----	----	----	1.00058	1.00058				
	tan δ	----	----	< 1	----	----	----	----	----	< 10	< 10				
1000 psi	ϵ'/ϵ_o	----	----	1.0403	----	----	----	----	----	1.0403	1.0403				
	tan δ	----	----	< 1	----	----	----	----	----	< 10	< 10				
2000 psi	ϵ'/ϵ_o	----	----	1.0807	----	----	----	----	----	1.0807	1.0807				
	tan δ	----	----	< 1	----	----	----	----	----	< 10	< 10				
3000 psi	ϵ'/ϵ_o	----	----	1.210	----	----	----	----	----	1.210	1.210				
	tan δ	----	----	< 1	----	----	----	----	----	< 10	< 10				
4000 psi	ϵ'/ϵ_o	----	----	1.563	----	----	----	----	----	1.563	1.563				
	tan δ	----	----	< 1	----	----	----	----	----	< 10	< 10				
5000 psi	ϵ'/ϵ_o	----	----	1.857	----	----	----	----	----	1.857	1.857				
	tan δ	----	----	< 1	----	----	----	----	----	< 10	< 10				
Nitrous oxide 14.7 psi[c]	ϵ'/ϵ_o	----	----	1.0030	----	----	----	----	----	1.0030	1.0030				
	tan δ	----	----	< 1	----	----	----	----	----	< 10	< 10				

a. Dow-Corning. b. Purified (Air Reduction). c. Olin Mathieson.

II. SUPPLEMENT TO DATA AT ROOM TEMPERATURE

A. Materials measured too late for inclusion in Section I

Values of tan δ are multiplied by 10^4; frequency given in c/s.

Ceramics		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$
"AFC" Alumina[a]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	8.28
	tan δ	----	----	----	----	----	----	----	----	----	----	9.4
"AlSiMag" 544[b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	7.69
(Supercedes previous sample)	tan δ	----	----	----	----	----	----	----	----	----	----	16
"AlSiMag" 548 dried[b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	5.51
	tan δ	----	----	----	----	----	----	----	----	----	----	1.0
"AlSiMag" 602 (dried)[c]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	4.62
	tan δ	----	----	----	----	----	----	----	----	----	----	18
"AlSiMag" 652[b]	ϵ'/ϵ_o	9.21	9.19	9.18	9.18	9.18	9.18	9.18				
	tan δ	74	11.5	4.2	2	0.8	0.15	< 1				
Beryllium oxide, hot pressed[d]	ϵ'/ϵ_o	5.58*	5.57*	5.55*	5.54*	5.54*	5.54*	5.54*	----	----	----	5.62
(d = 2.560 gm/cc)	tan δ	110*	34*	5*	3*	1.8*	1.3*	1.8*	----	----	----	10.4
Beryllium oxide, crucible grade[d]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	3.55
(d = 1.784 gm/cc)	tan δ	----	----	----	----	----	----	----	----	----	----	14.9
Coors AI-200 (1956 production)	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	8.63
	tan δ	----	----	----	----	----	----	----	----	----	----	11.6
"Alite" AP-212[e]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	8.25
	tan δ	----	----	----	----	----	----	----	----	----	----	8.6
"Alite" AP-216[e]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	8.03
	tan δ	----	----	----	----	----	----	----	----	----	----	13
"Alite" AP-312[e]	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	8.42
	tan δ	----	----	----	----	----	----	----	----	----	----	11.5

a. Amer. Feldmuehle. b. Alumina (Amer. Lava). c. Lava (Amer. Lava). d. Beryllium Corp. e. Alumina (U.S. Stoneware).

*Mottled sample d = 2.546.

II. SUPPLEMENT TO DATA AT ROOM TEMPERATURE (Cont.)

A. Materials measured too late for inclusion in Section I

Values of tan δ are multiplied by 10^4; frequency given in c/s.


Plastics		$1x10^2$	$1x10^3$	$1x10^4$	$1x10^5$	$1x10^6$	$1x10^7$	$1x10^8$	$3x10^8$	$1x10^9$	$3x10^9$	$8.6x10^9$
"Markite" 3985	ϵ'/ϵ_o	----	----	----	----	----	----	----	----	----	----	40
	tan δ	----	----	>400*	> 20*	> 10*	> 60*	----	----	----	----	3.0*
	(ohm-cm)	----	1.73	1.73	1.73	1.73	----	----	----	----	----	1.7
"Markite" 12812	ϵ'/ϵ_o	----	----	----	----	----	1200	----	----	----	----	21
	tan δ	----	----	$>10^{5}$*	----	----	> 5*	----	----	----	----	1.5*
	(ohm-cm)	----	16.4	16.4	16.0	15.8	----	----	----	----	----	6.6
"Scotchply" 1002, isotropic[a]	ϵ'/ϵ_o	----	----	----	----	----	----	----	4.56	4.53	4.51	4.48
	tan δ	----	----	----	----	----	----	----	158	162	167	175
"Scotchply" 1002, crossply[a]	ϵ'/ϵ_o	----	----	----	----	----	----	----	4.42	4.40	4.39	4.38
	tan δ	----	----	----	----	----	----	----	164	177	186	200
"Scotchply" 1002, unidirectional[a]	ϵ'/ϵ_o	----	----	----	----	----	----	----	4.35	4.32	4.28	4.24
	tan δ	----	----	----	----	----	----	----	171	171	172	173
"Scotchply" XPM-107[b]	ϵ'/ϵ_o	----	----	----	----	----	----	----	4.31	4.30	4.29	4.28
	tan δ	----	----	----	----	----	----	----	129	162	181	202

a. Polyester "fiberglas" laminate (Minn. Mining) b. Epoxy - "fiberglas" laminate (Minn. Mining).

*tan δ not mulitplied by 10^4.


II B.

Dielectric Constant vs. Density for High Alumina Bodies at 26°C

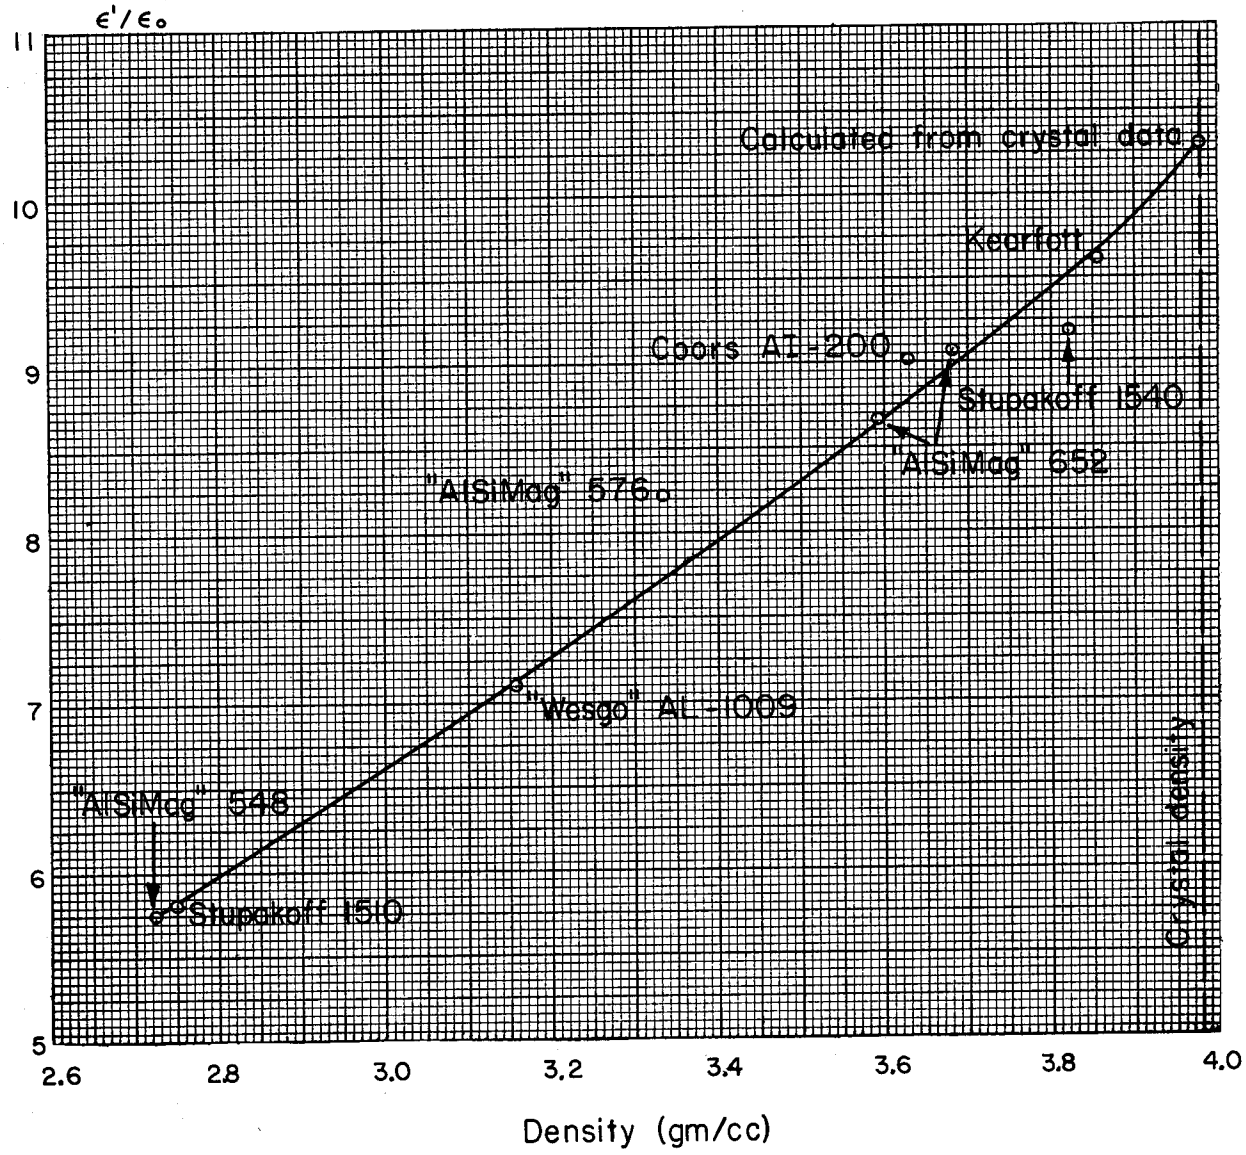


II B.

Dielectric Constant vs. Density for Beryllia Bodies at 26°C

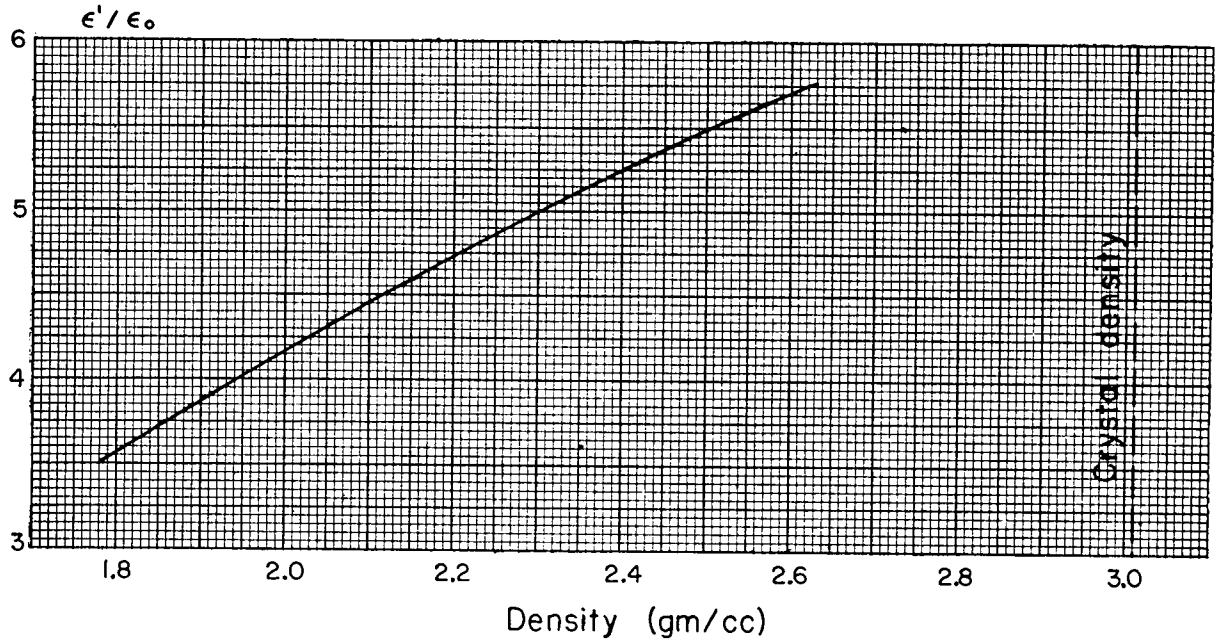

Dielectric Constant vs. Density for "Teflon" at 26°C

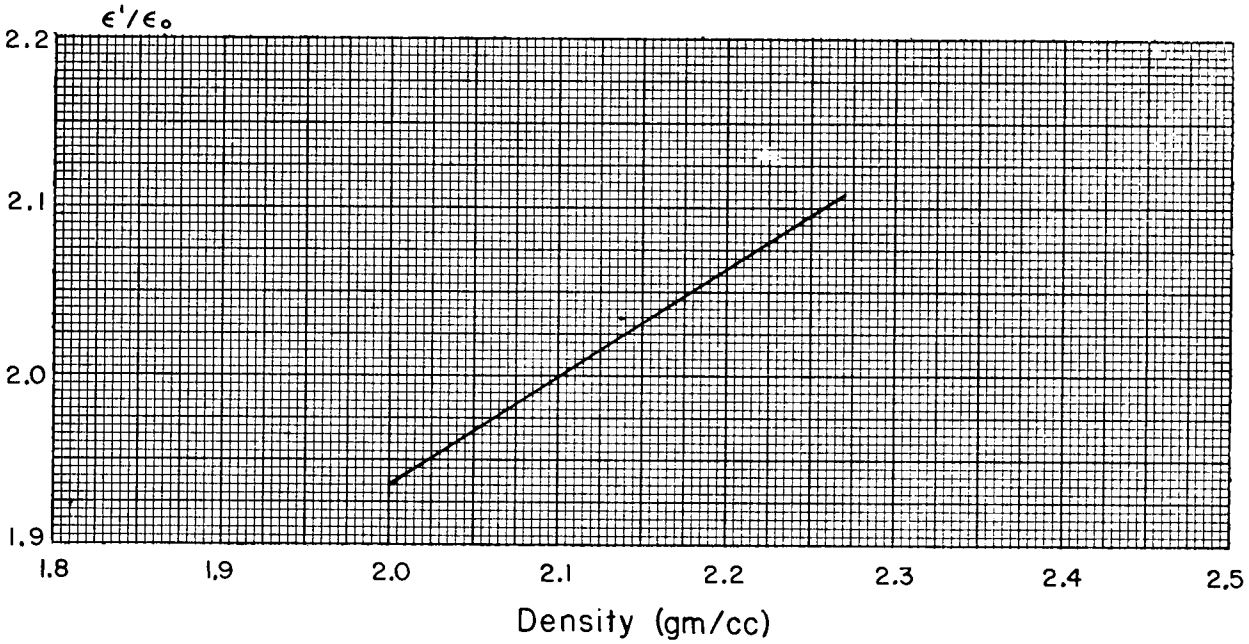

III. Data at Fixed Frequencies as a Function of Temperature

Previous to this volume of the "Tables," the highest temperature of measurements has not exceeded, with few exceptions, the long-time thermal stability temperature for each material.

In the present volume, data have been taken on several laminates at temperatures above normal, For these, the time intervals of measurement are indicated. The samples were measured in partial vacuum in order to withdraw gaseous decomposition products.

Other curves showing data with increasing and decreasing temperatures, particularly with ceramics, indicate changes due to water loss since the sample is not in equilibrium with room humidity at the end of the run. The change in electrical properties with water loss is a reversible process more easily demonstrated in the microwave region, where it is mainly a volume effect, than at low frequencies where it is mainly a surface effect.


As in the room temperature measurements, the electric field direction is perpendicular to the plane of laminates for frequencies in the range 10^2 through 3×10^8 c/s; it is parallel to or in the plane of the laminate for all higher frequencies unless otherwise specified.

The measuring frequency for the curves marked $f = 10^{10}$ was 8.5 kMc.

III A 1. Crystals

Aluminum oxide crystal, sapphire
Field perpendicular to optical axis


Linde Air

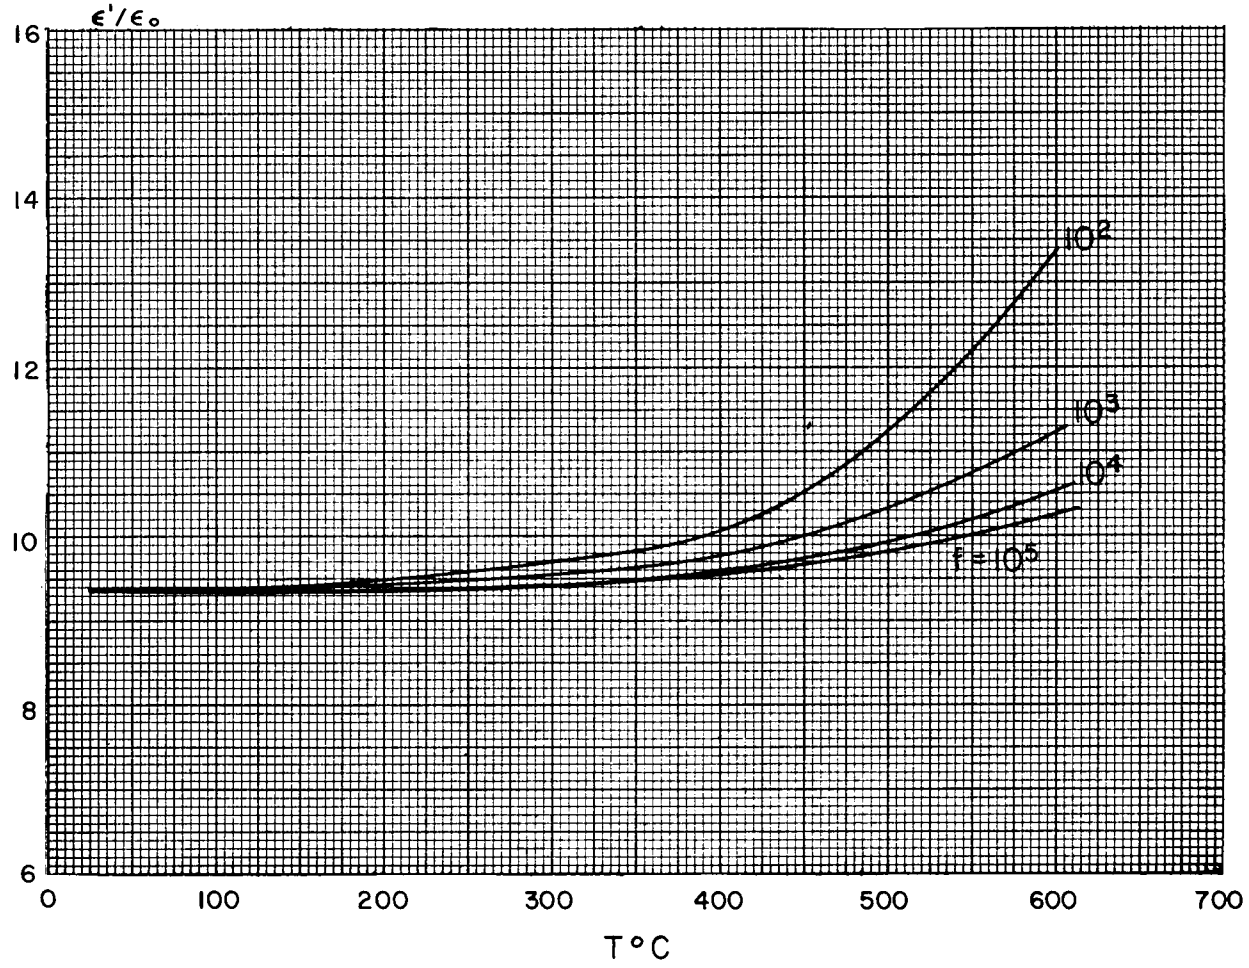

III A 1. Crystals

Aluminum oxide crystal, sapphire
Field perpendicular to optical axis


Linde Air

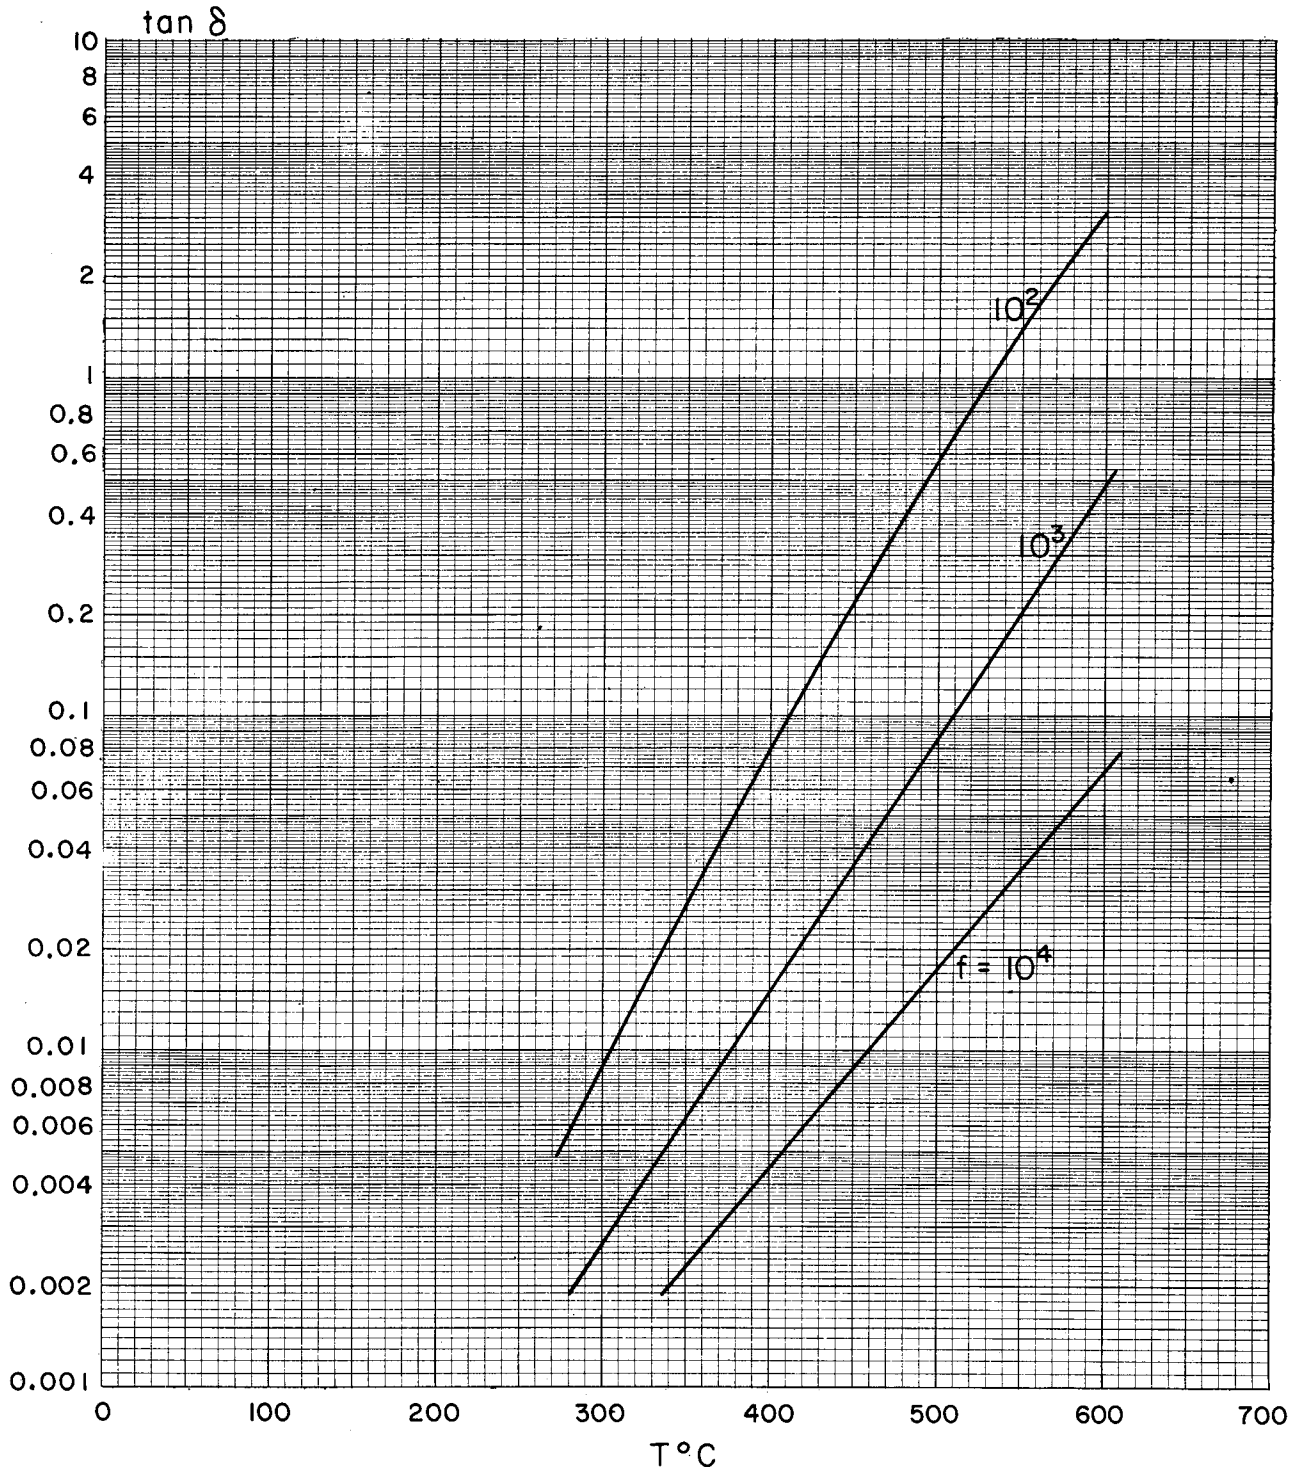

III A 1. Crystals


Aluminum oxide crystal (field parallel to optical axis)

Linde Air

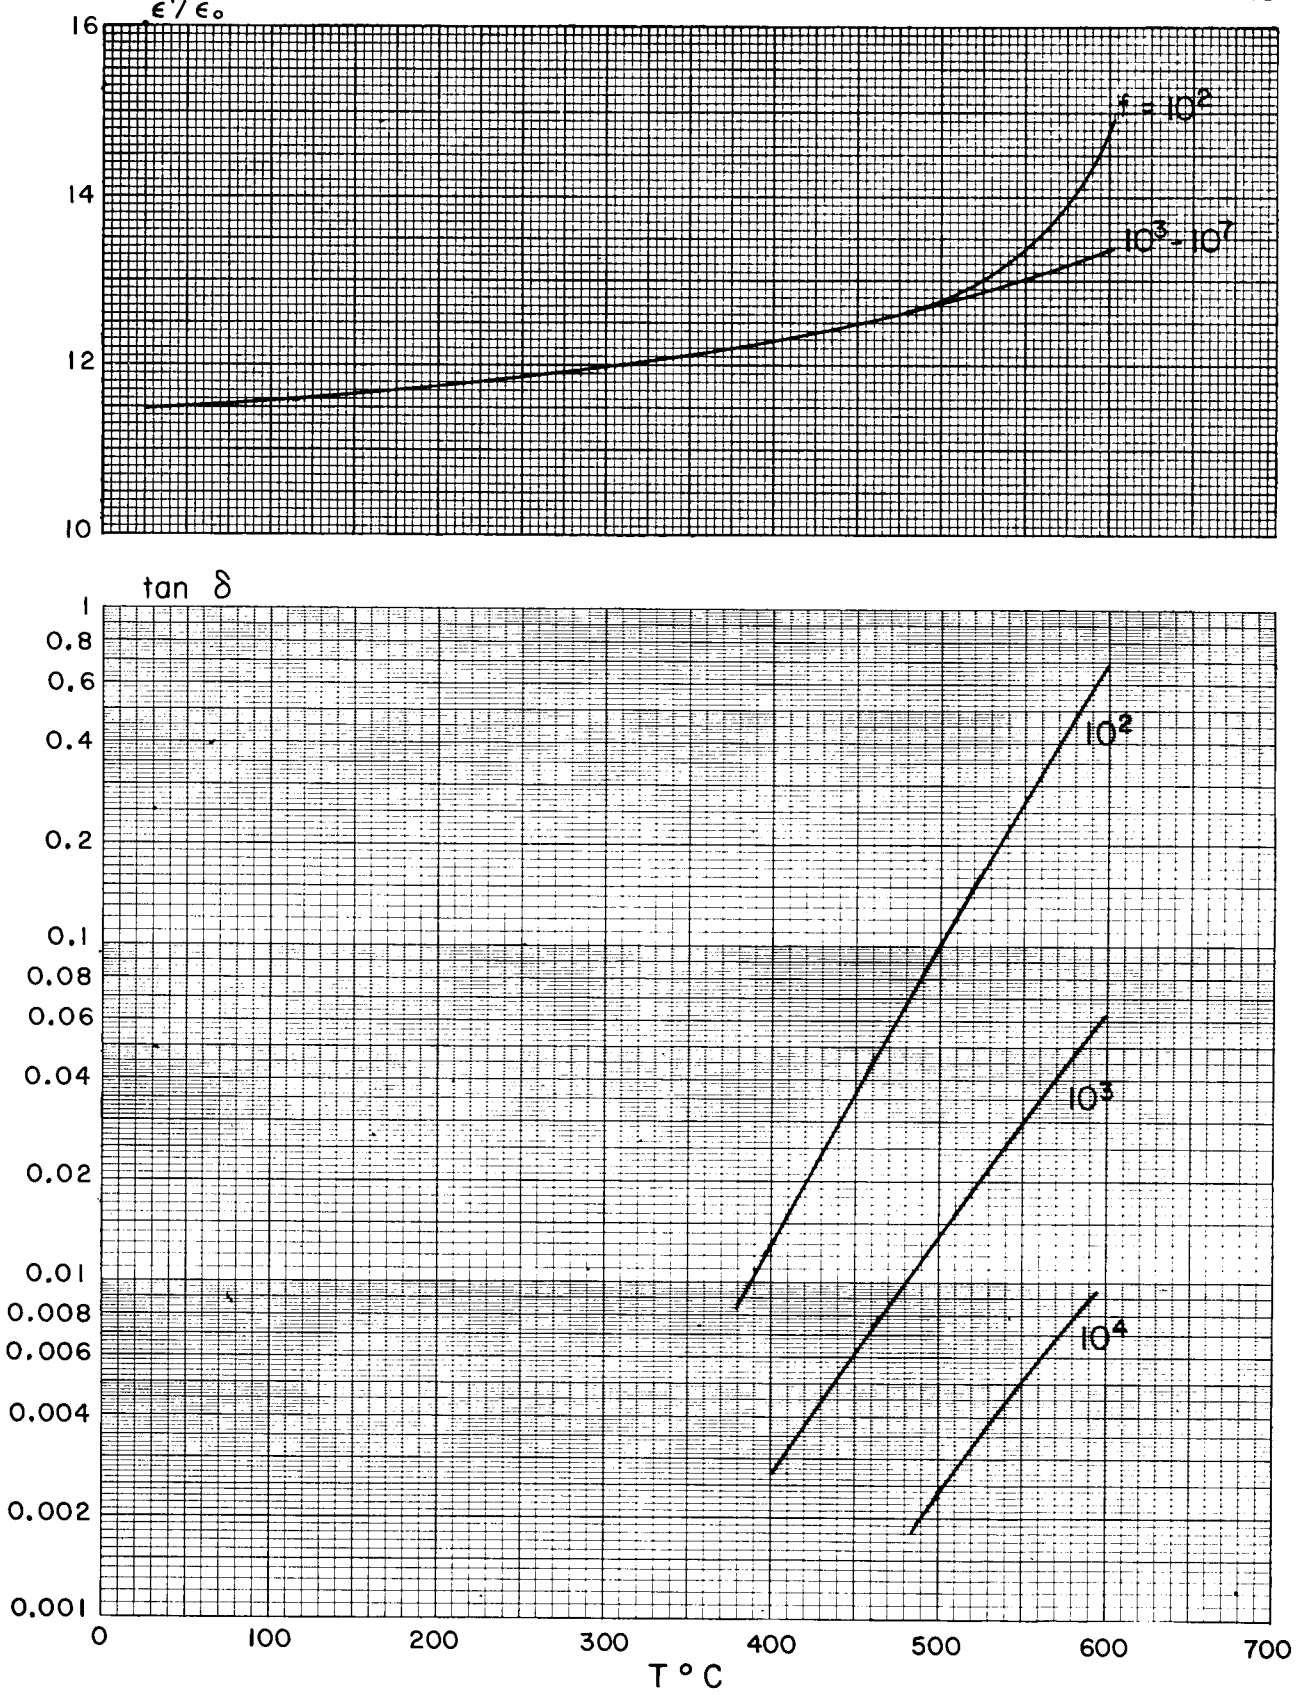


III A 1. Crystals

Magnesium oxide crystal — Norton

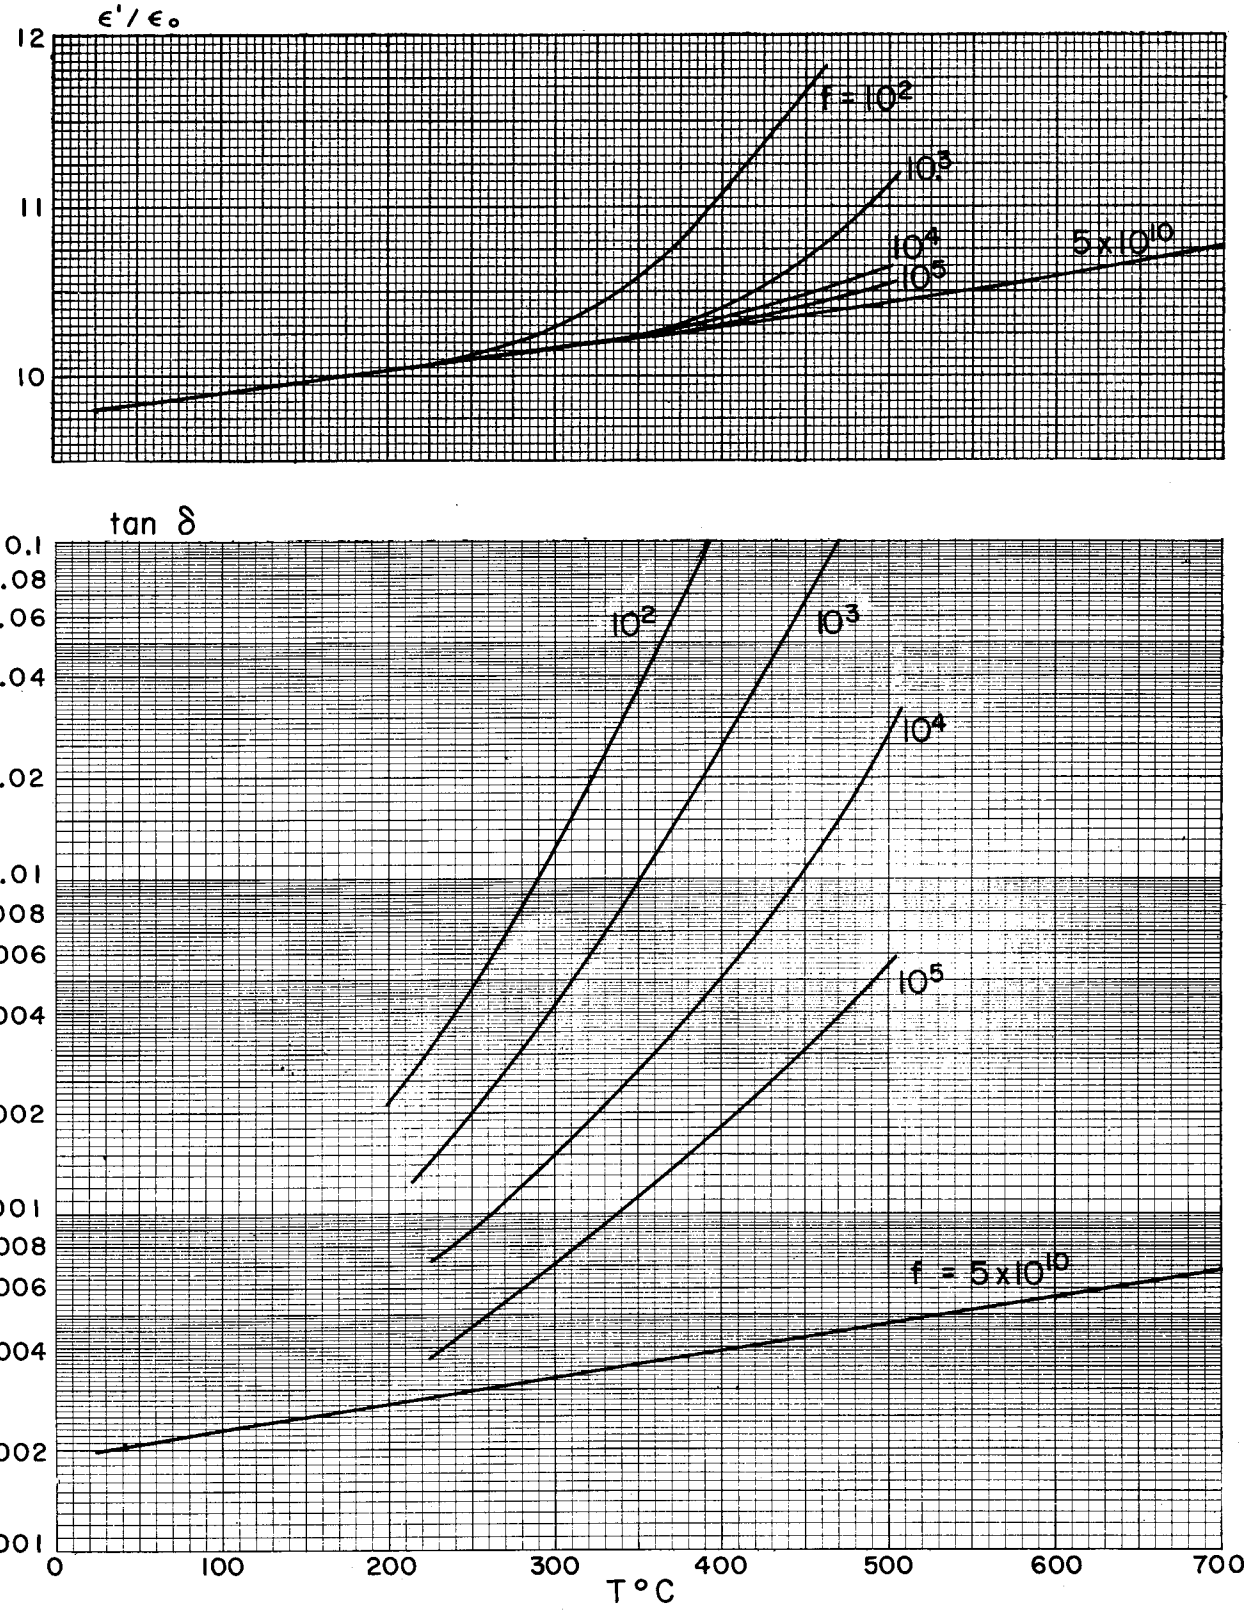


III A 1. Crystals

Potassium Chloride — Harshaw

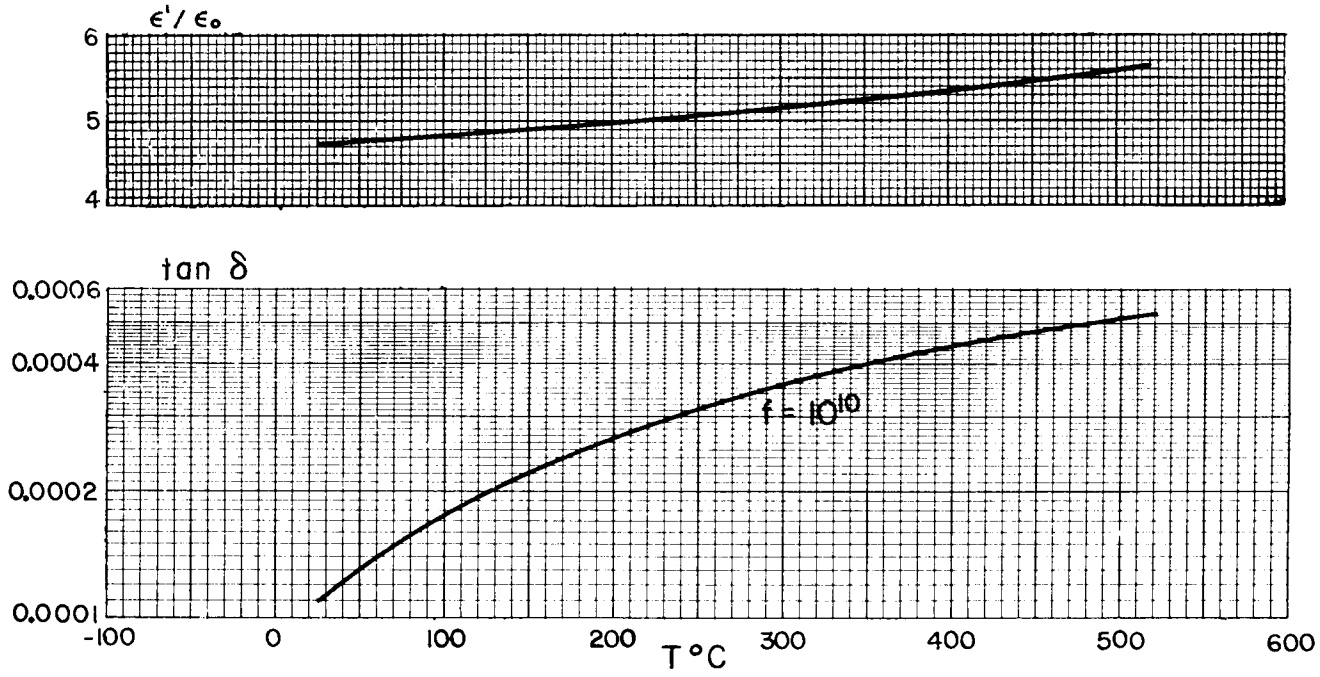


III A 2 a. Aluminas

"AFC" — American Feldmuehle

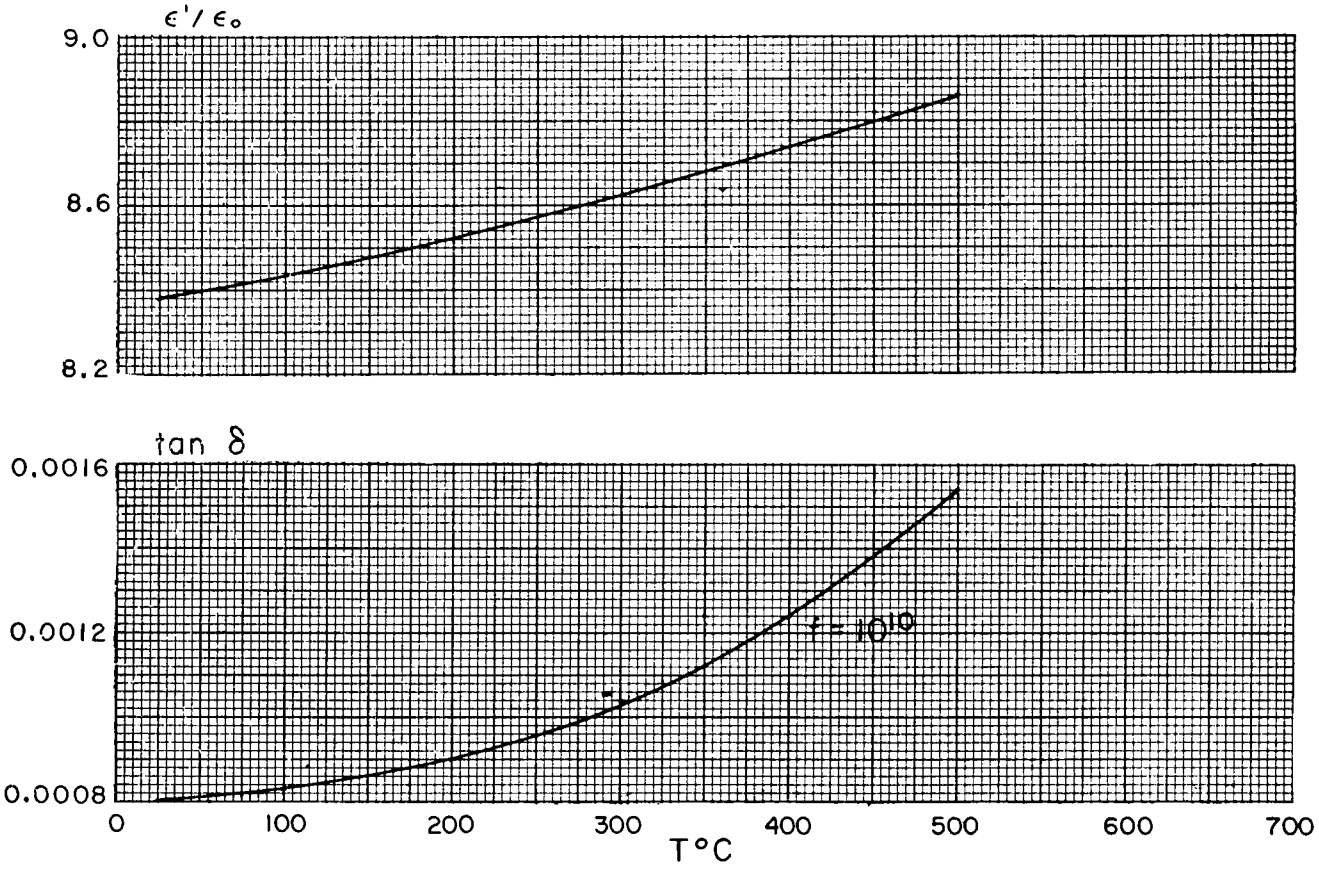


III A 2 a. Aluminas

"AlSiMag" 544 American Lava

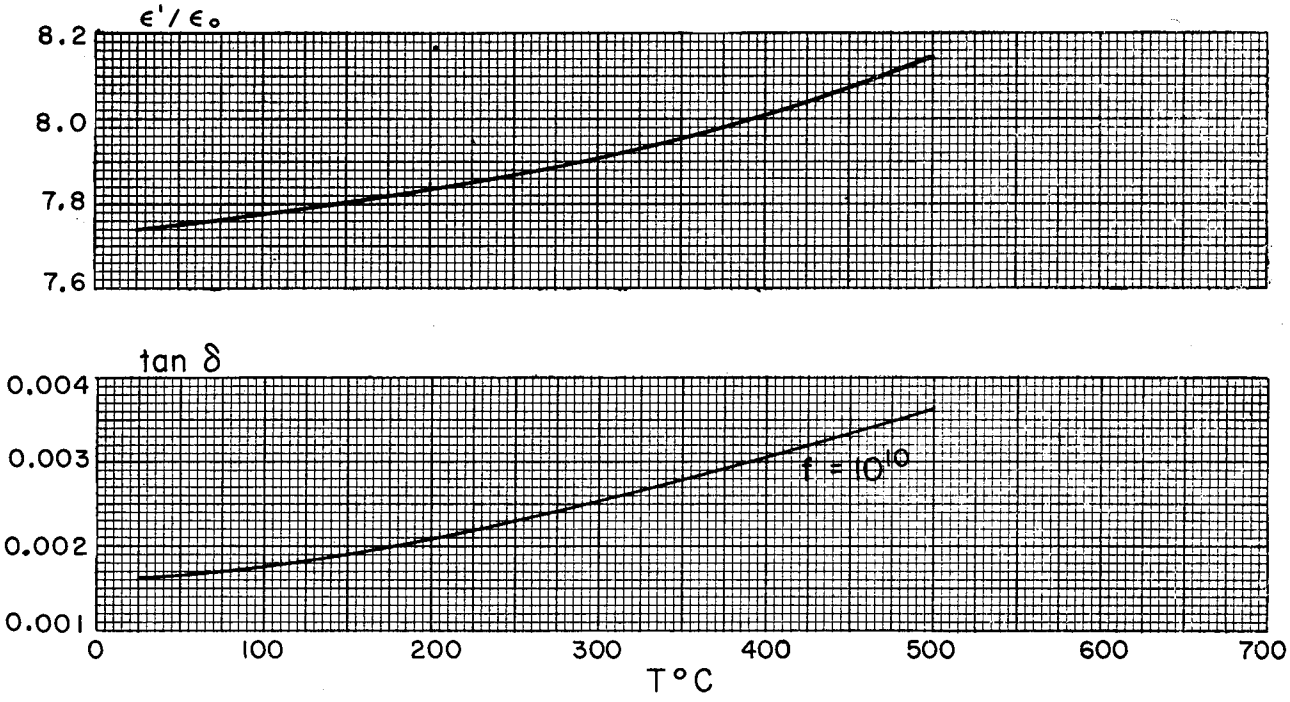


"AlSiMag" 548 American Lava

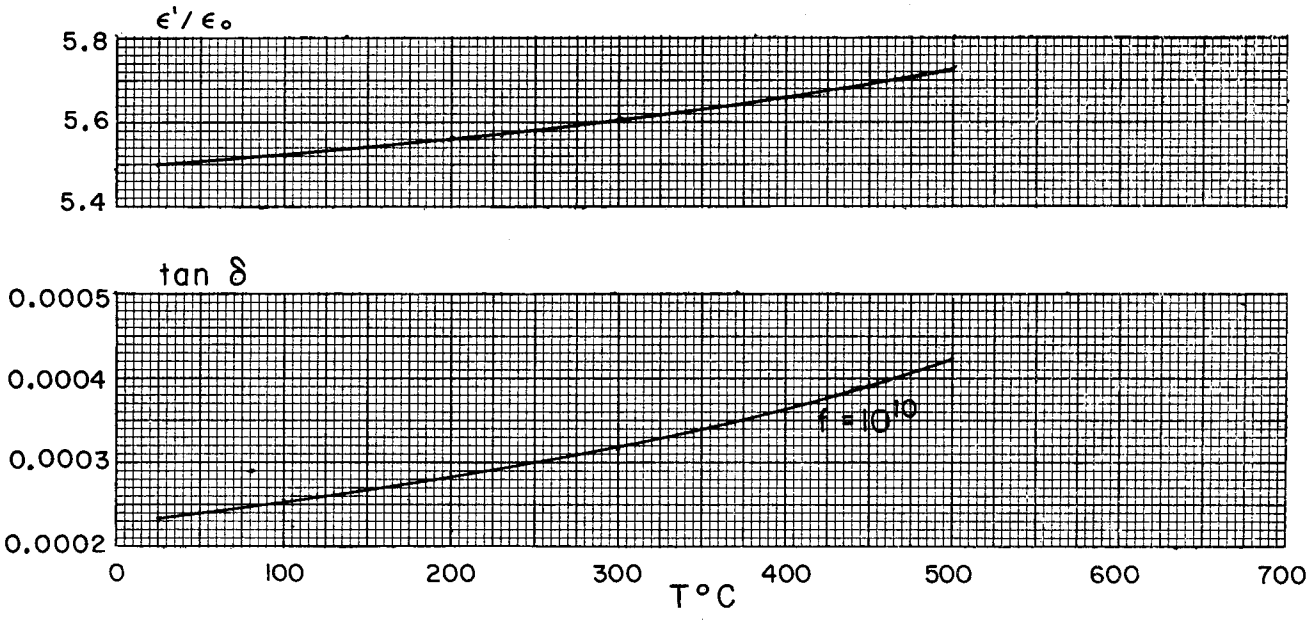


III A 2 a. Aluminas

"AlSiMag" 491 (blue) American Lava

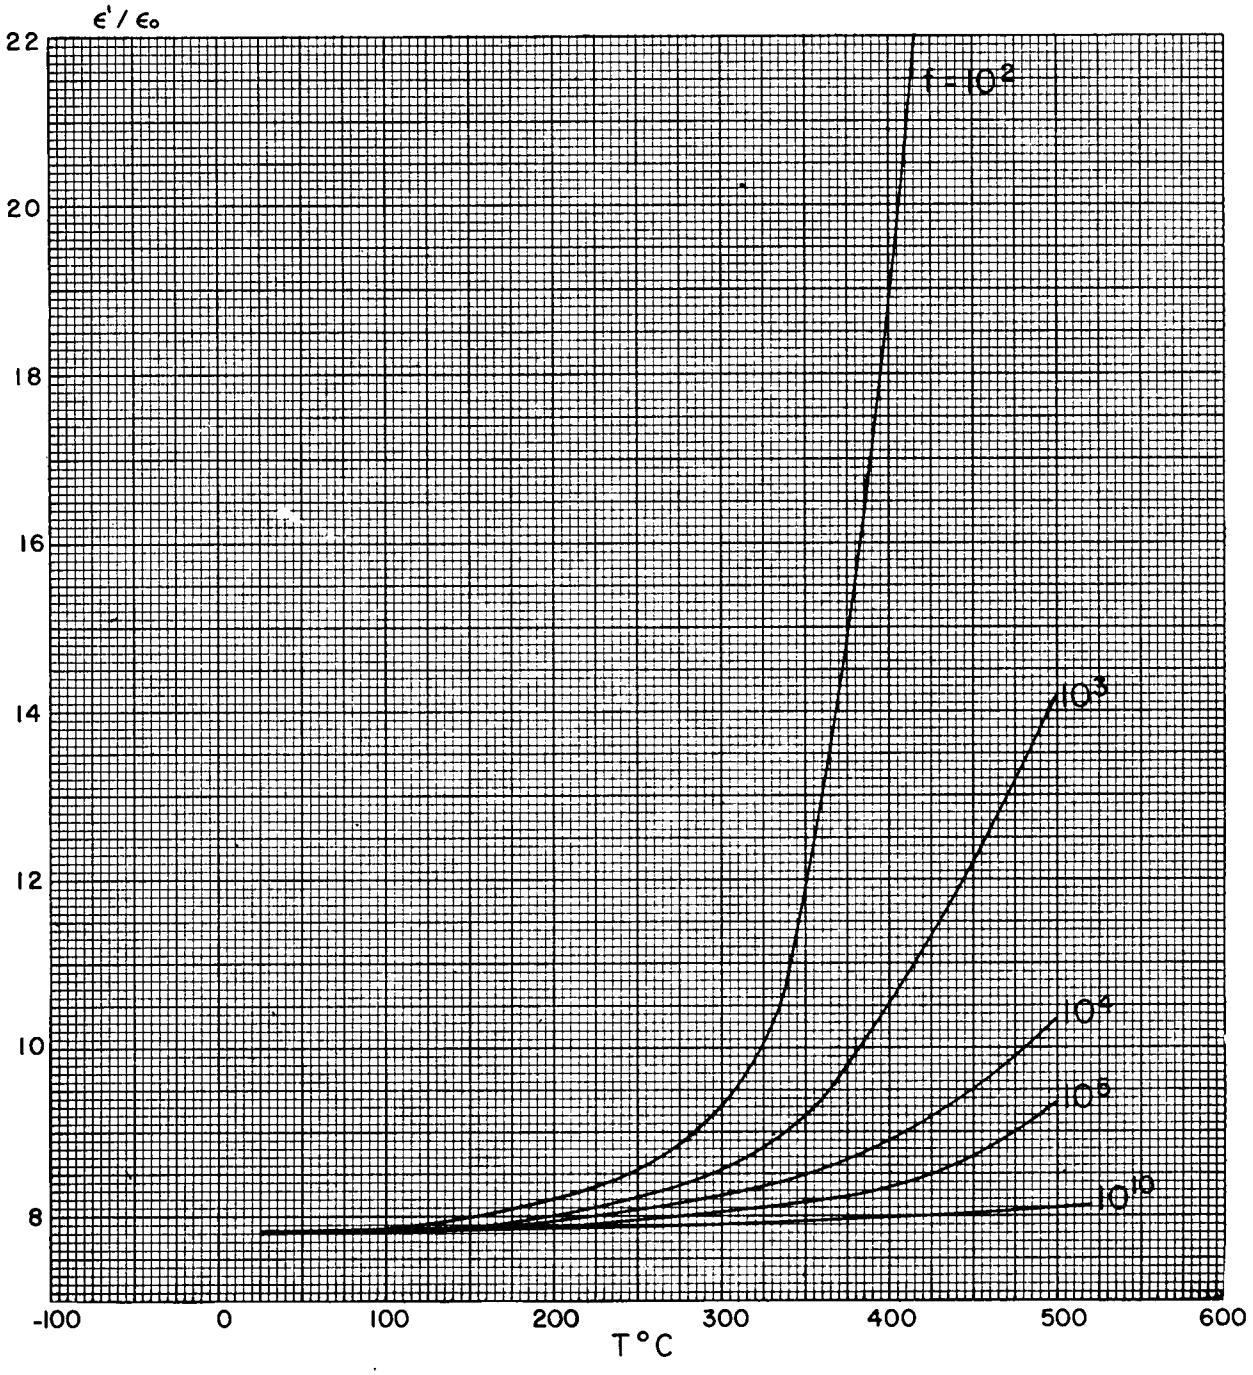


III A 2 a. Aluminas

"AlSiMag" 491 (blue) American Lava

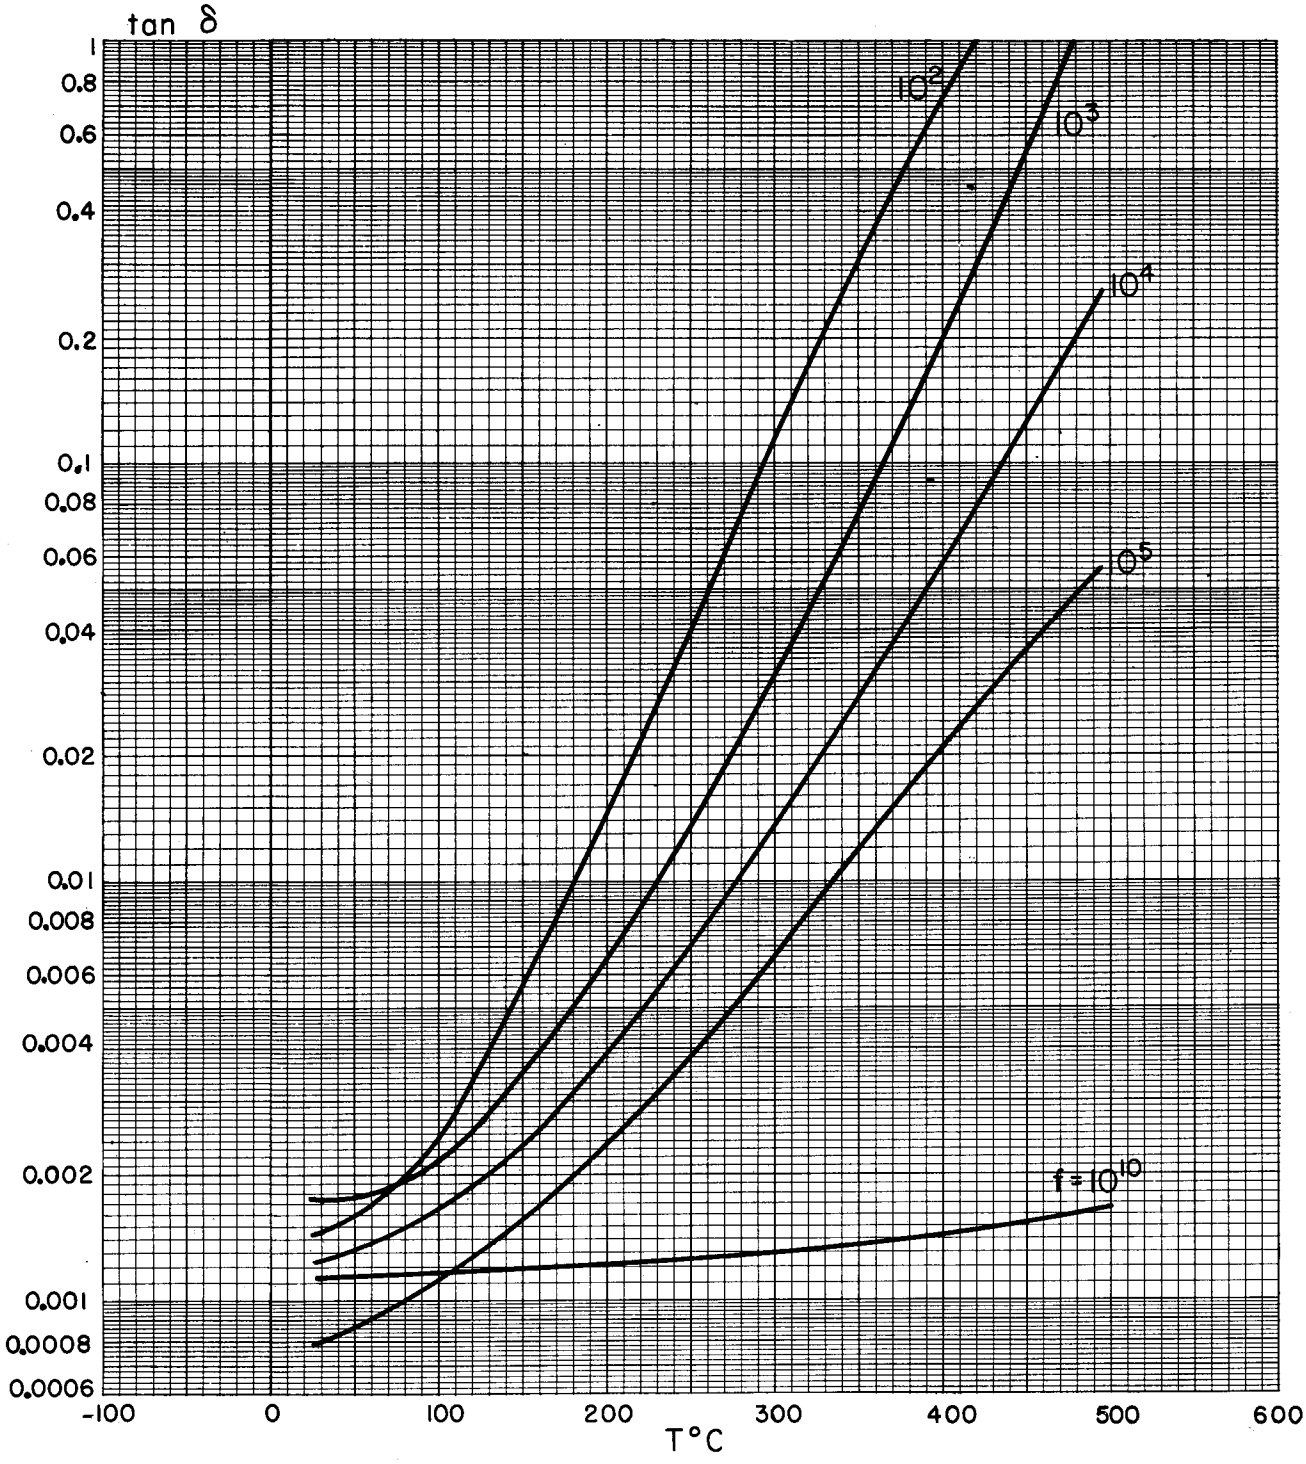


III A 2 a. Aluminas

"AlSiMag" 513 (pink) American Lava

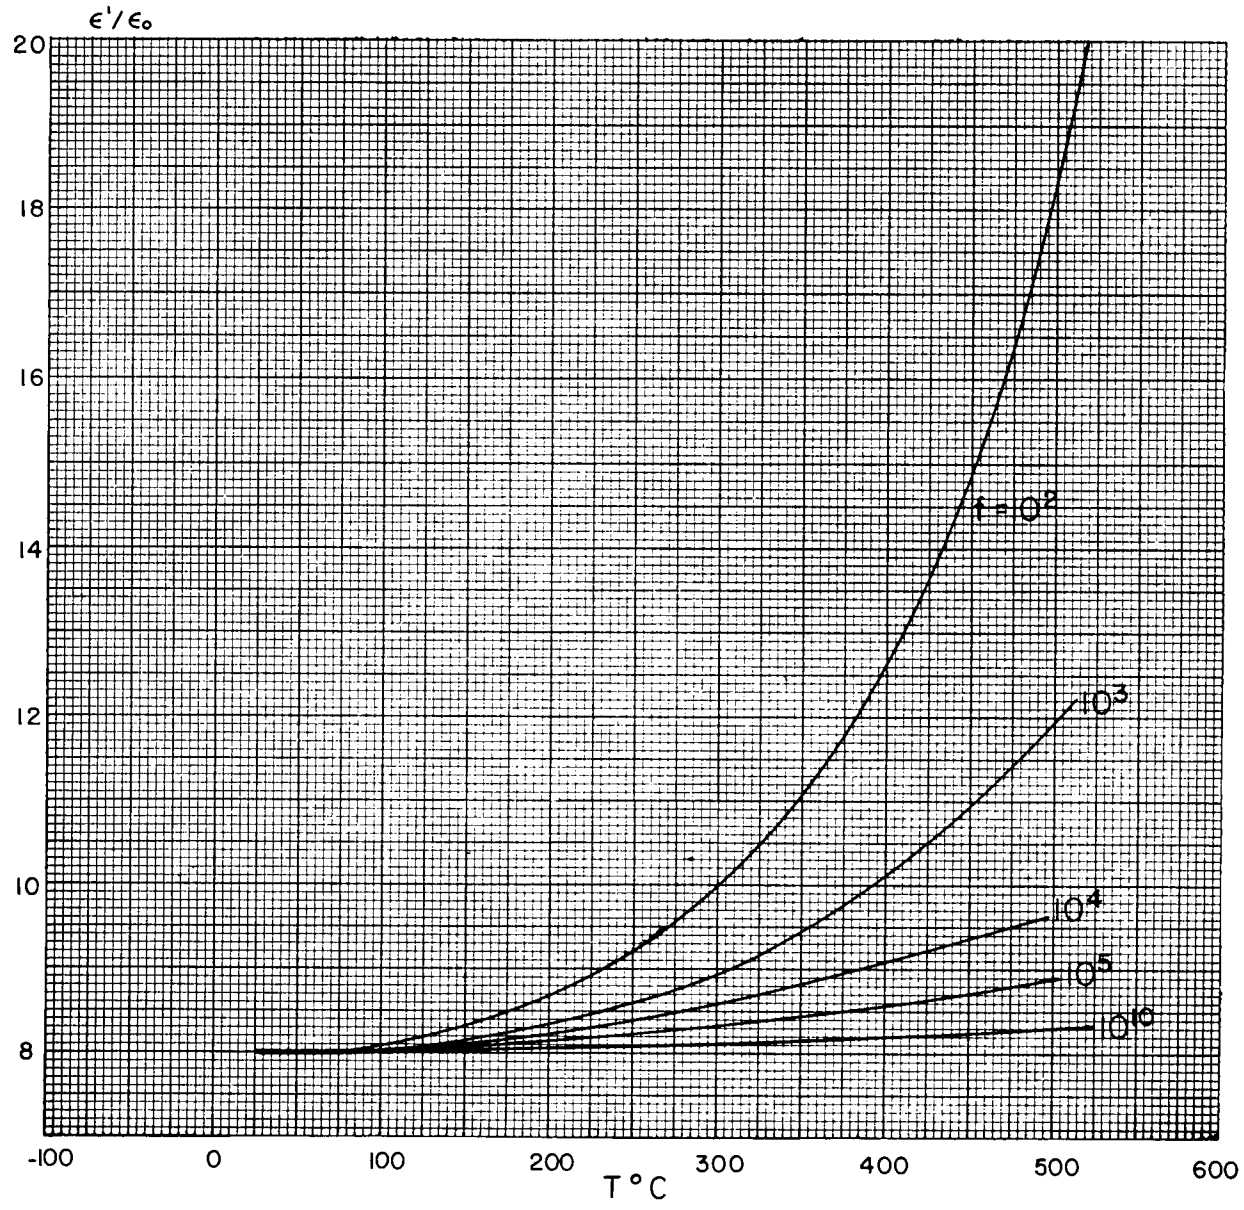


III A 2 a. Aluminas

"AlSiMag" 513 (pink) American Lava

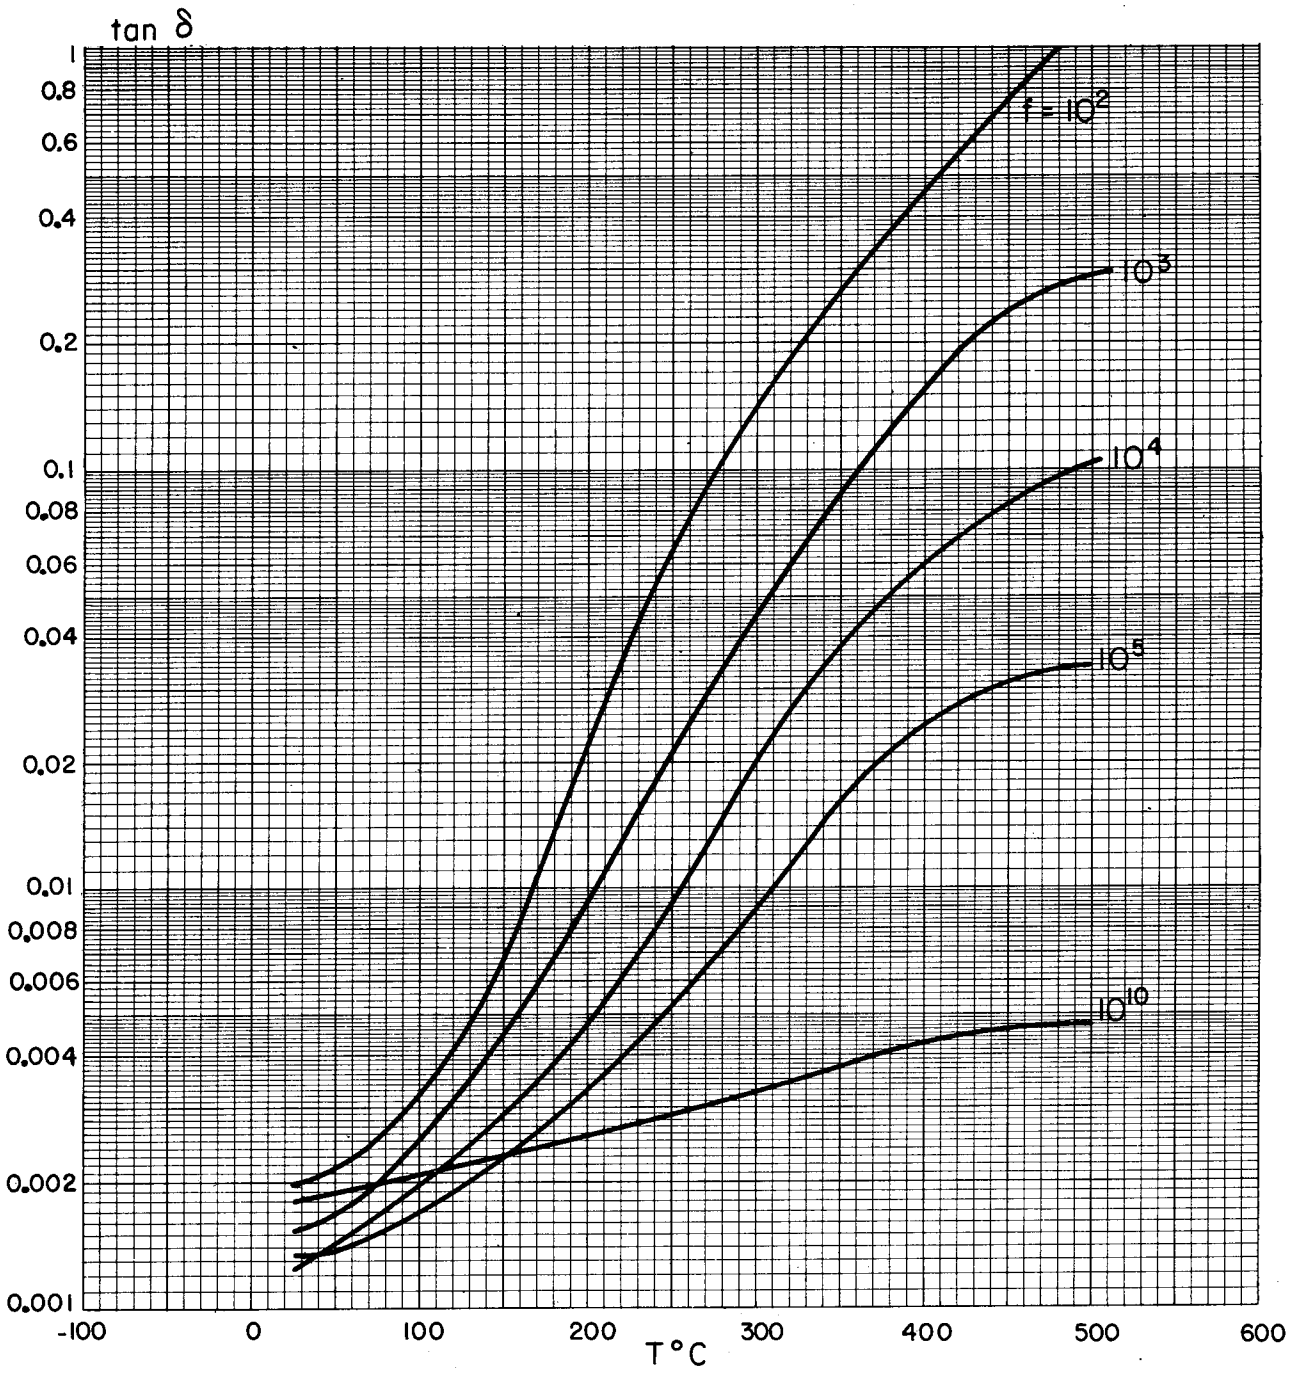


III A 2 a. Aluminas

"AlSiMag" 576 American Lava

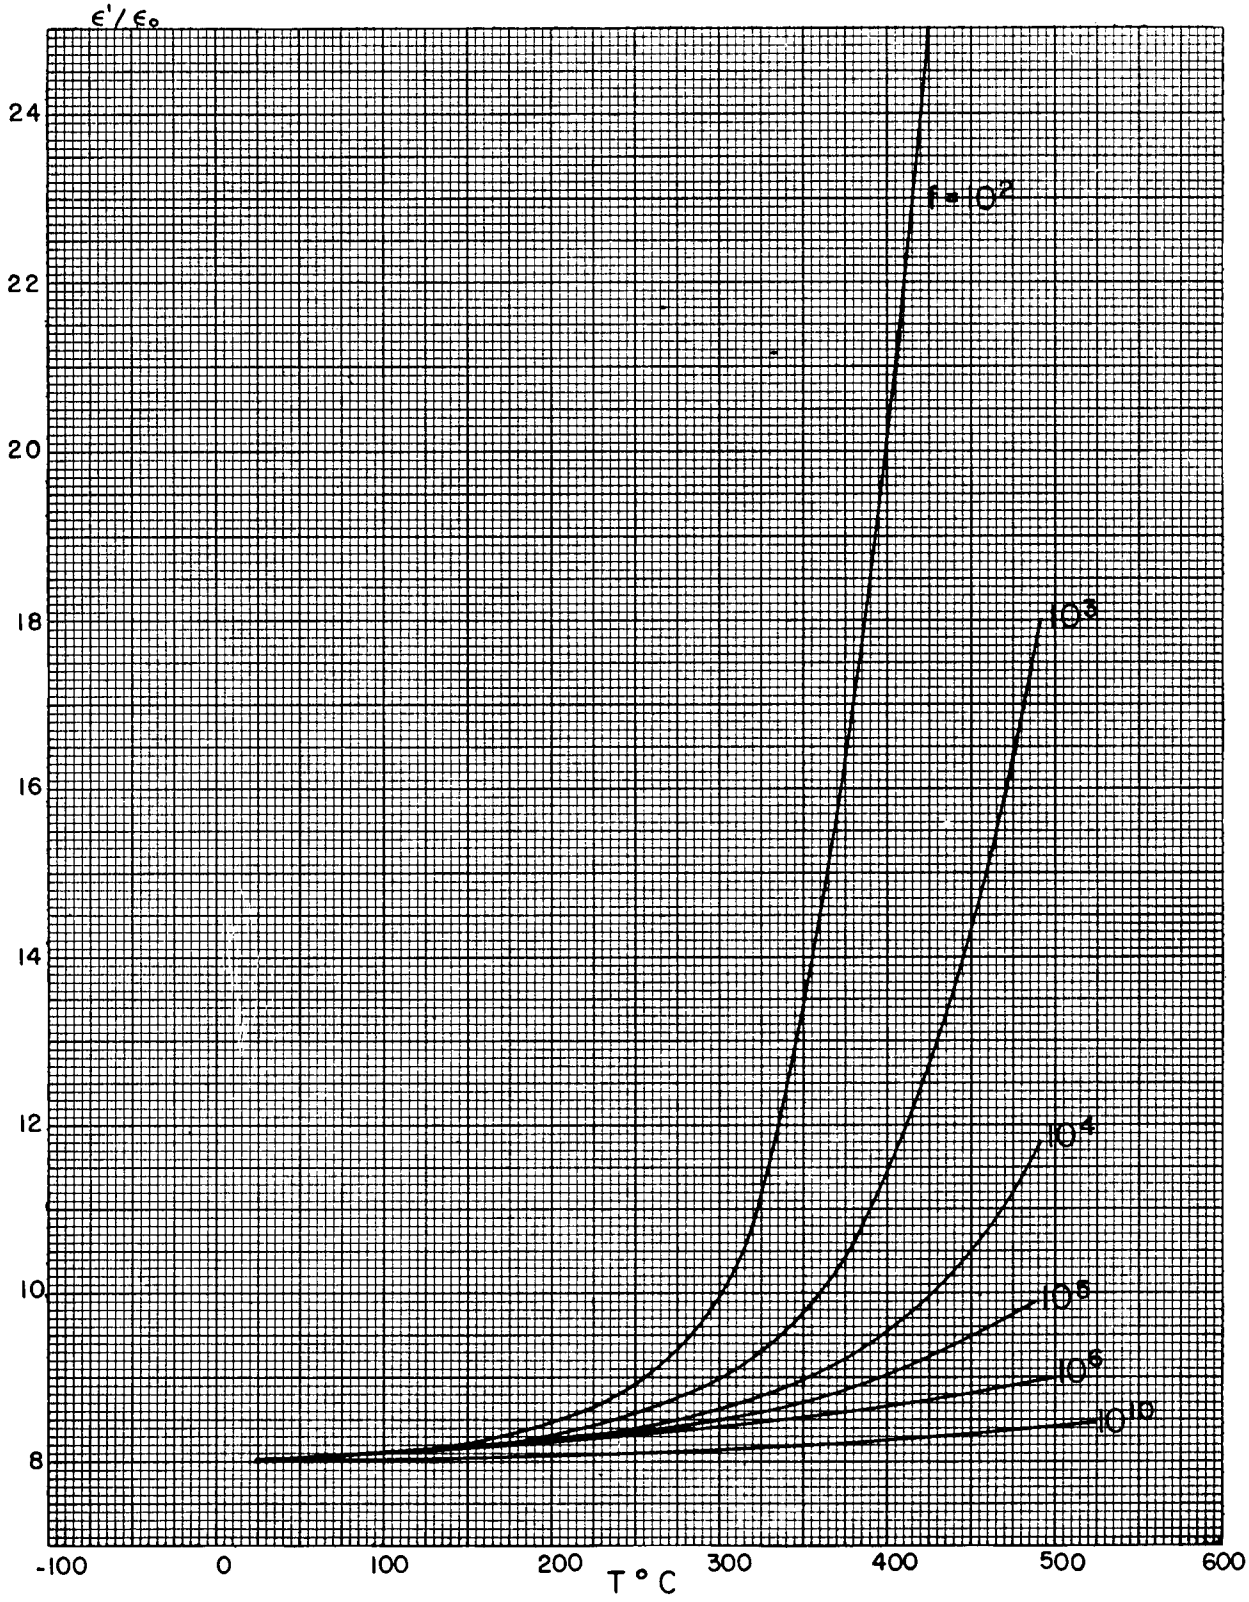


III A 2 a. Aluminas

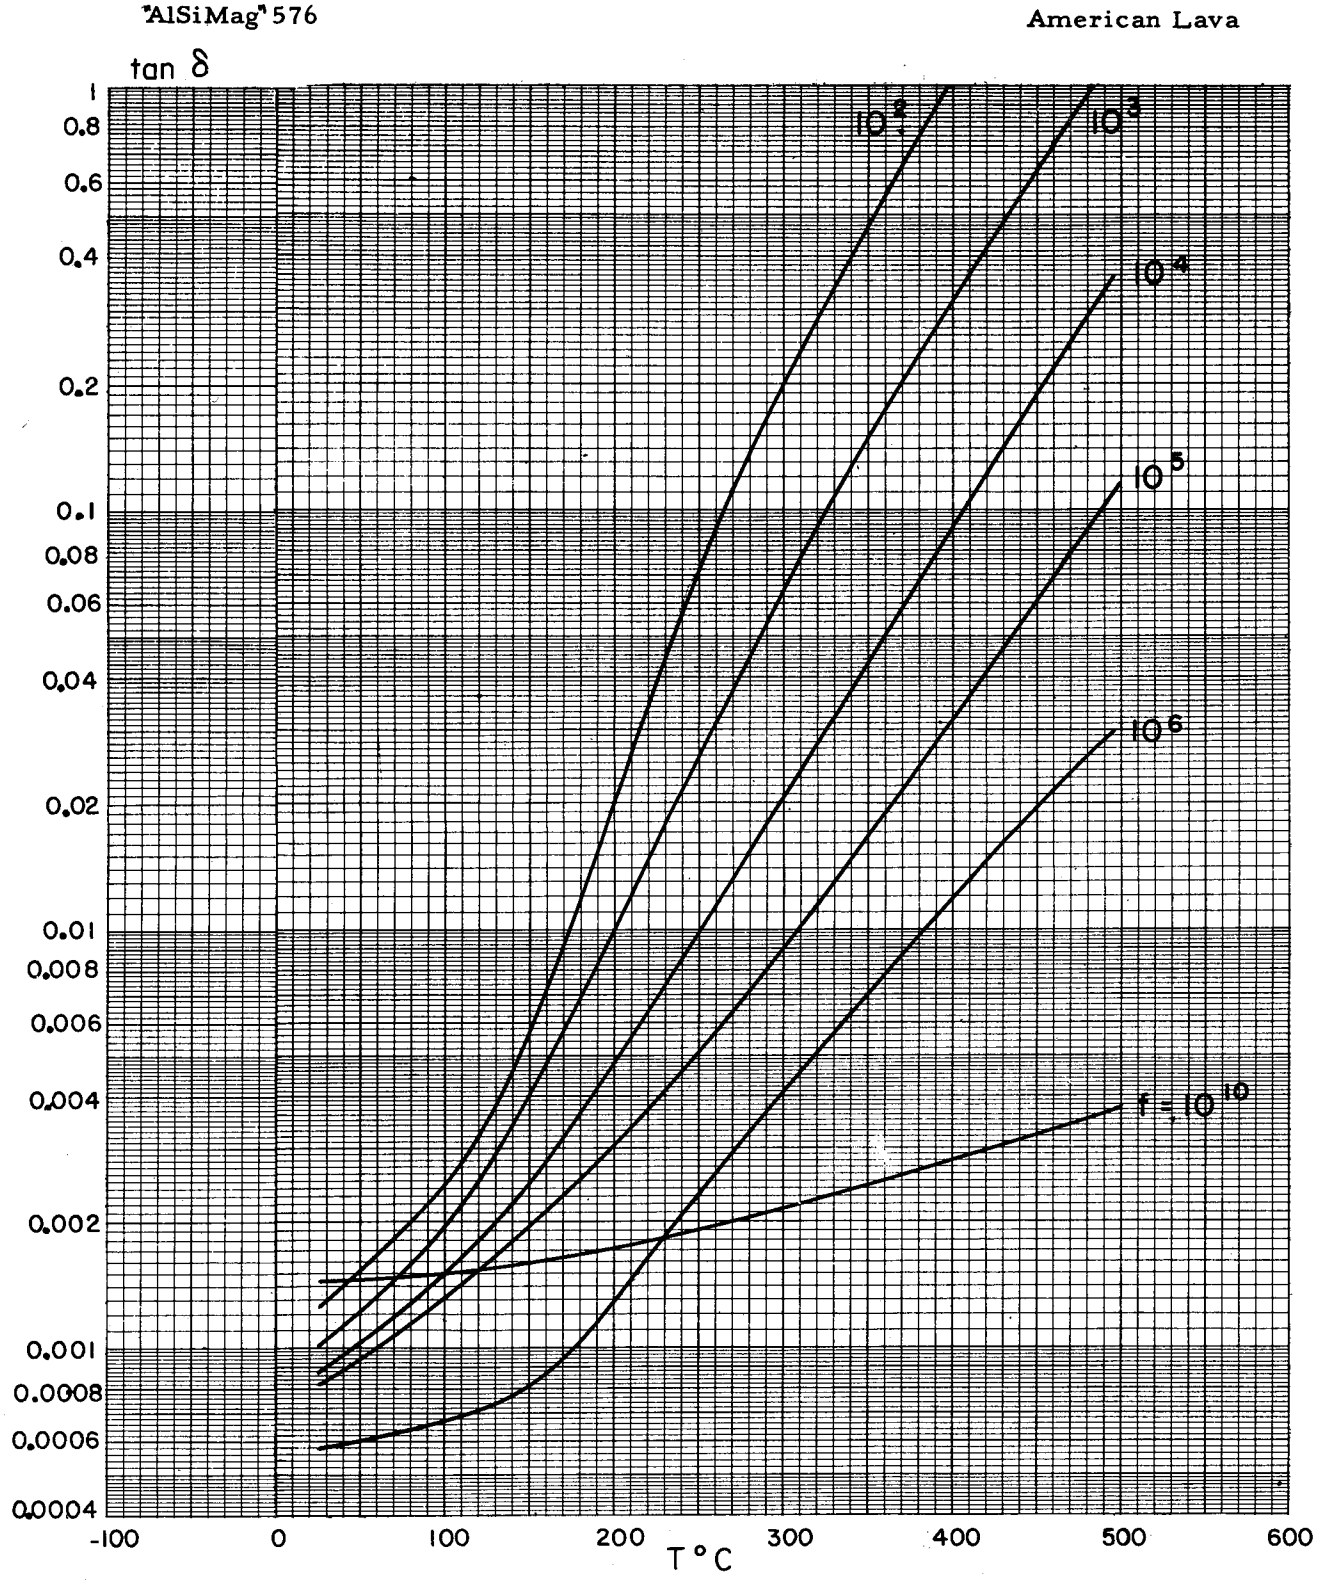


III A 2 a Aluminas

"AlSiMag" 652 American Lava

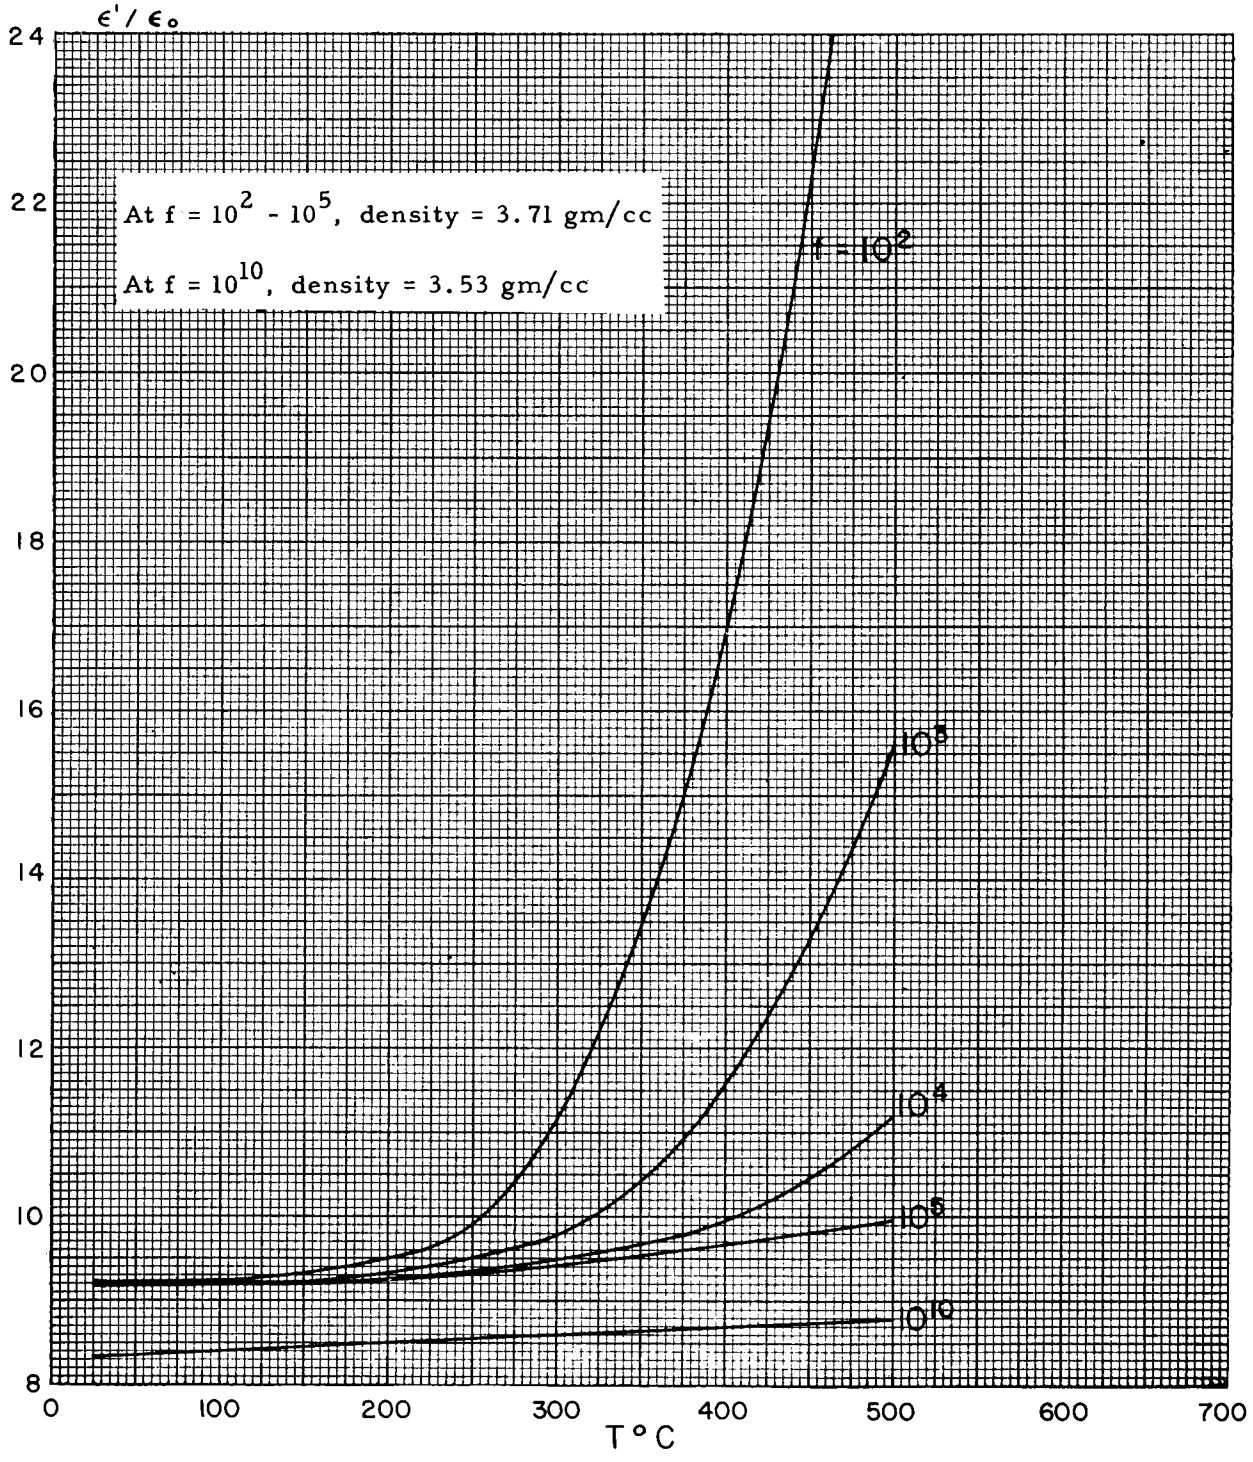

III A 2 a. Aluminas


"AlSiMag" 652 American Lava

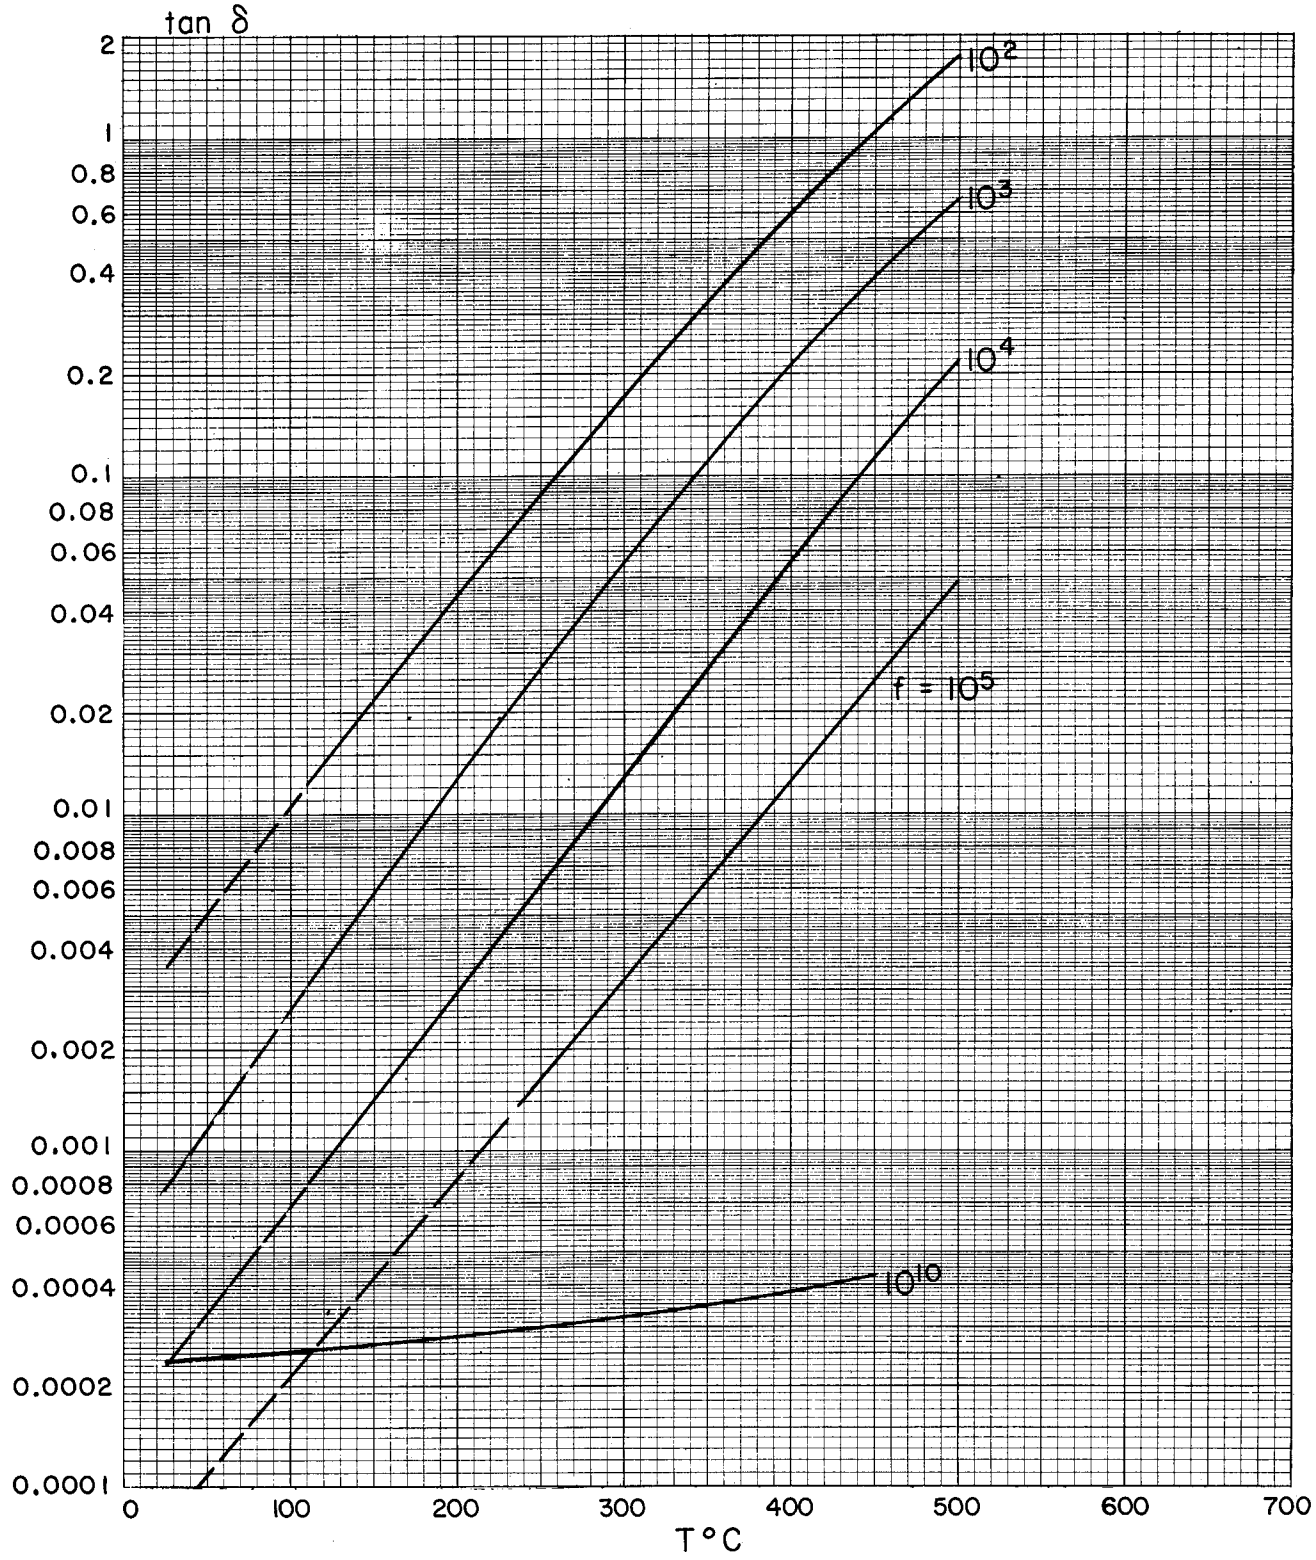

III A 2 a. Aluminas


Coors AL-100

Coors

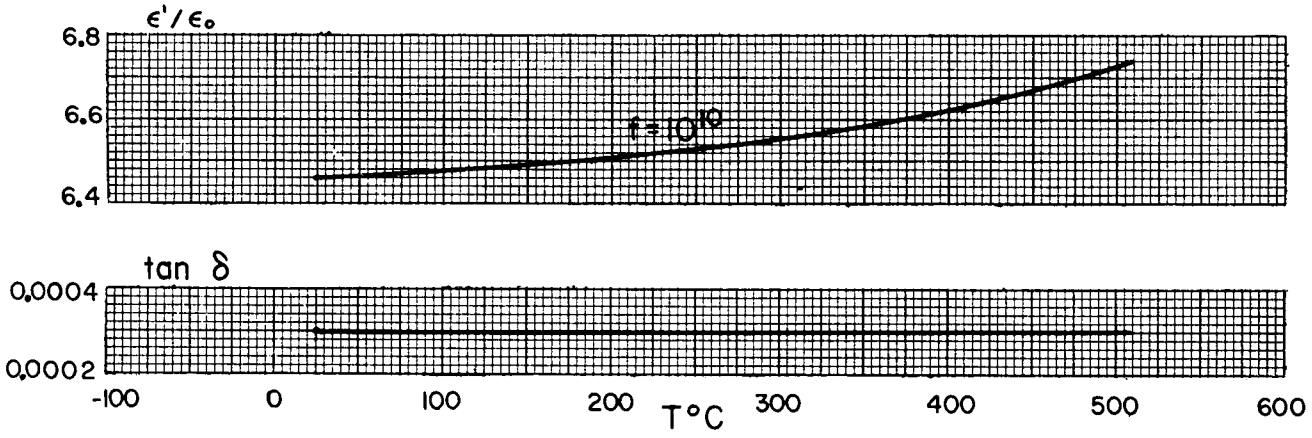


Coors AI-200 (1956)

Coors

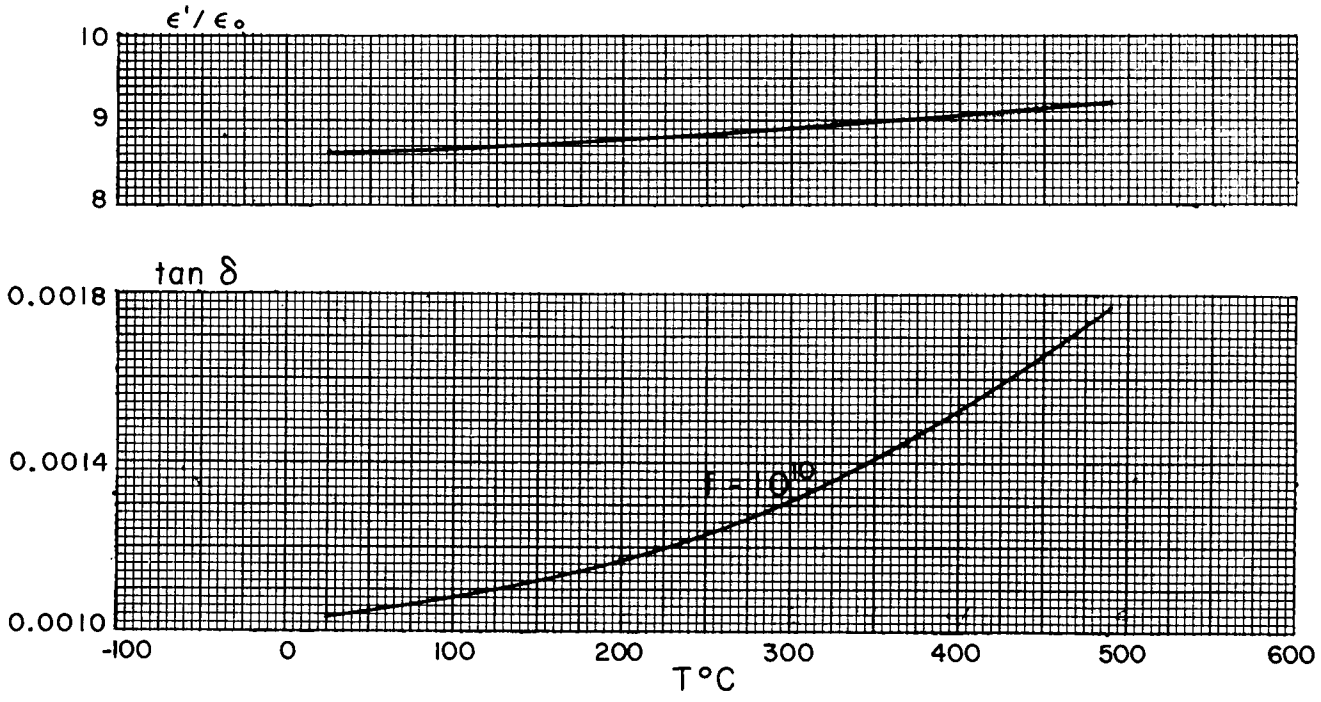


III A 2 a. Aluminas


Corning JD-40 Corning

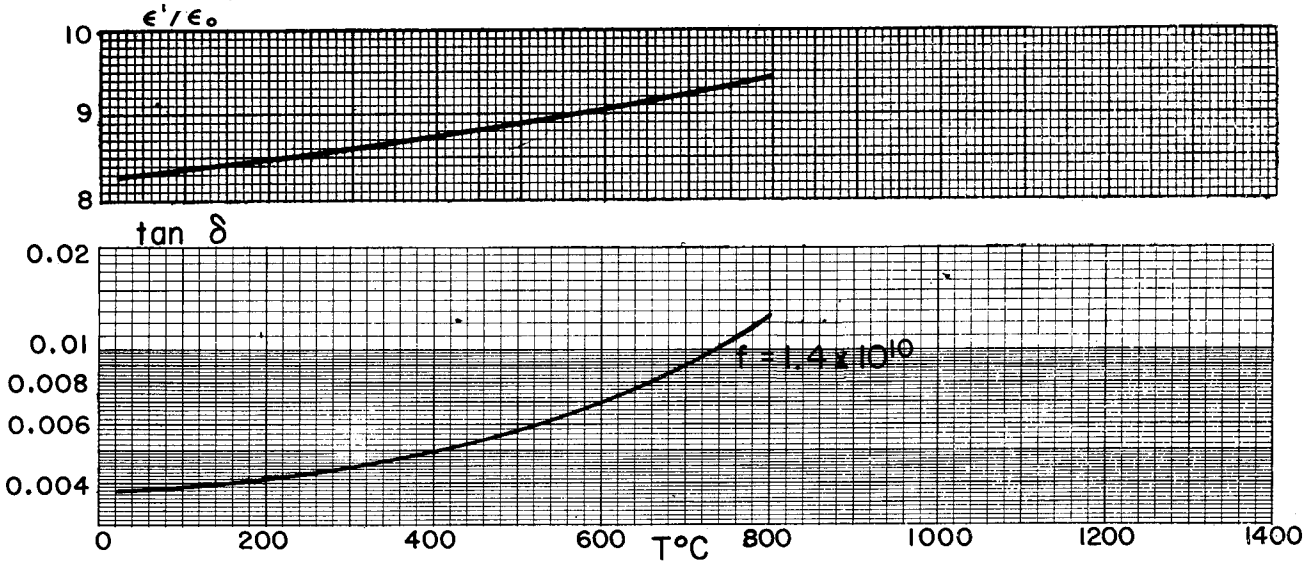

Corning JD-82 Corning

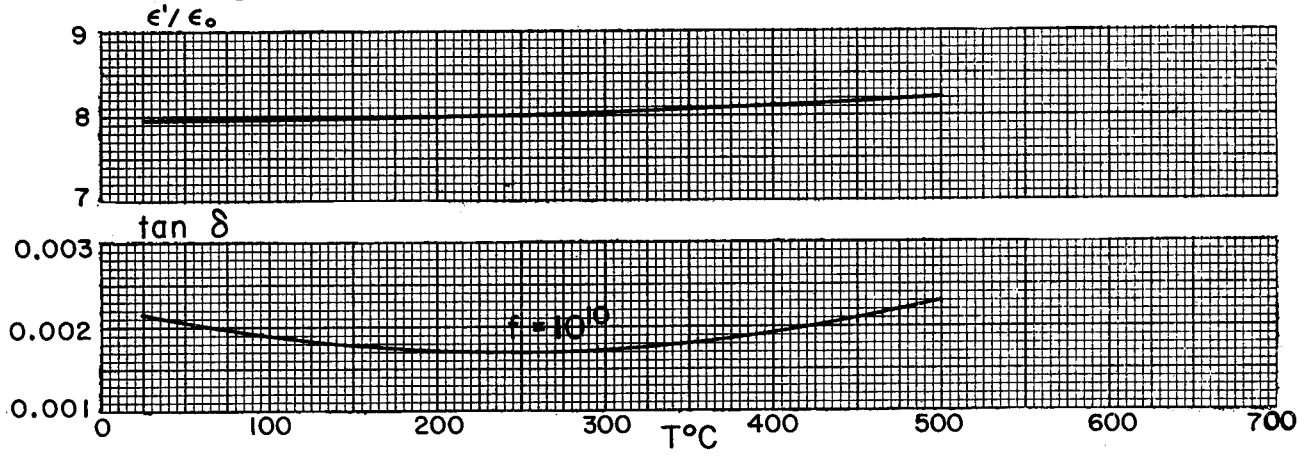


Corning JB-183 Corning

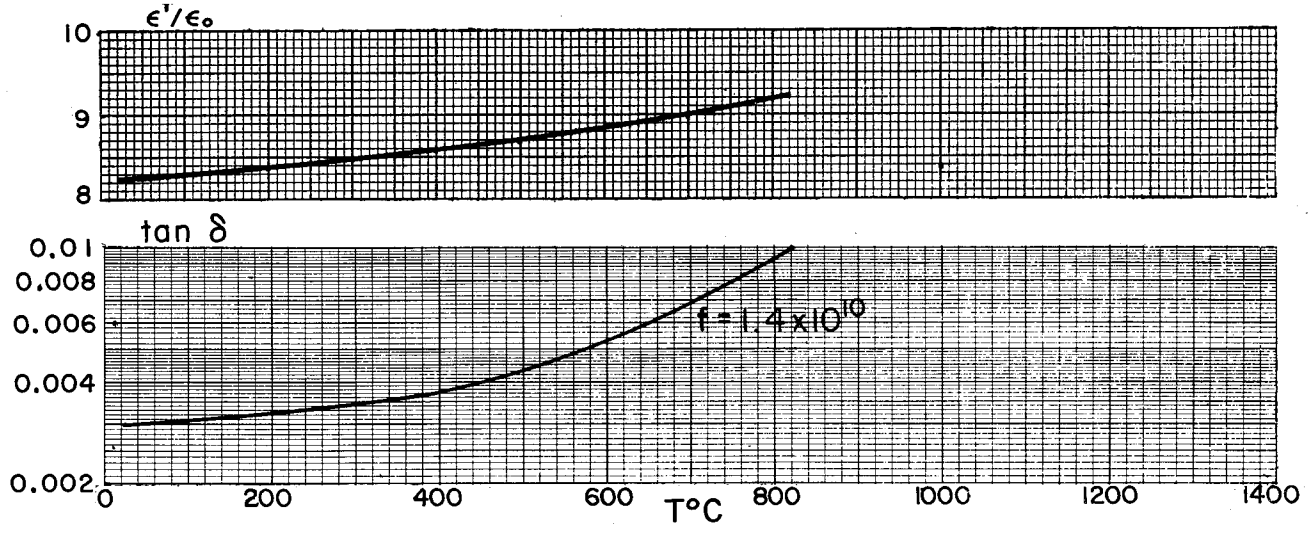

III A 2 a. Aluminas

"Diamonite" B-890


Diamonite Products Div.
U.S. Ceramic Tile

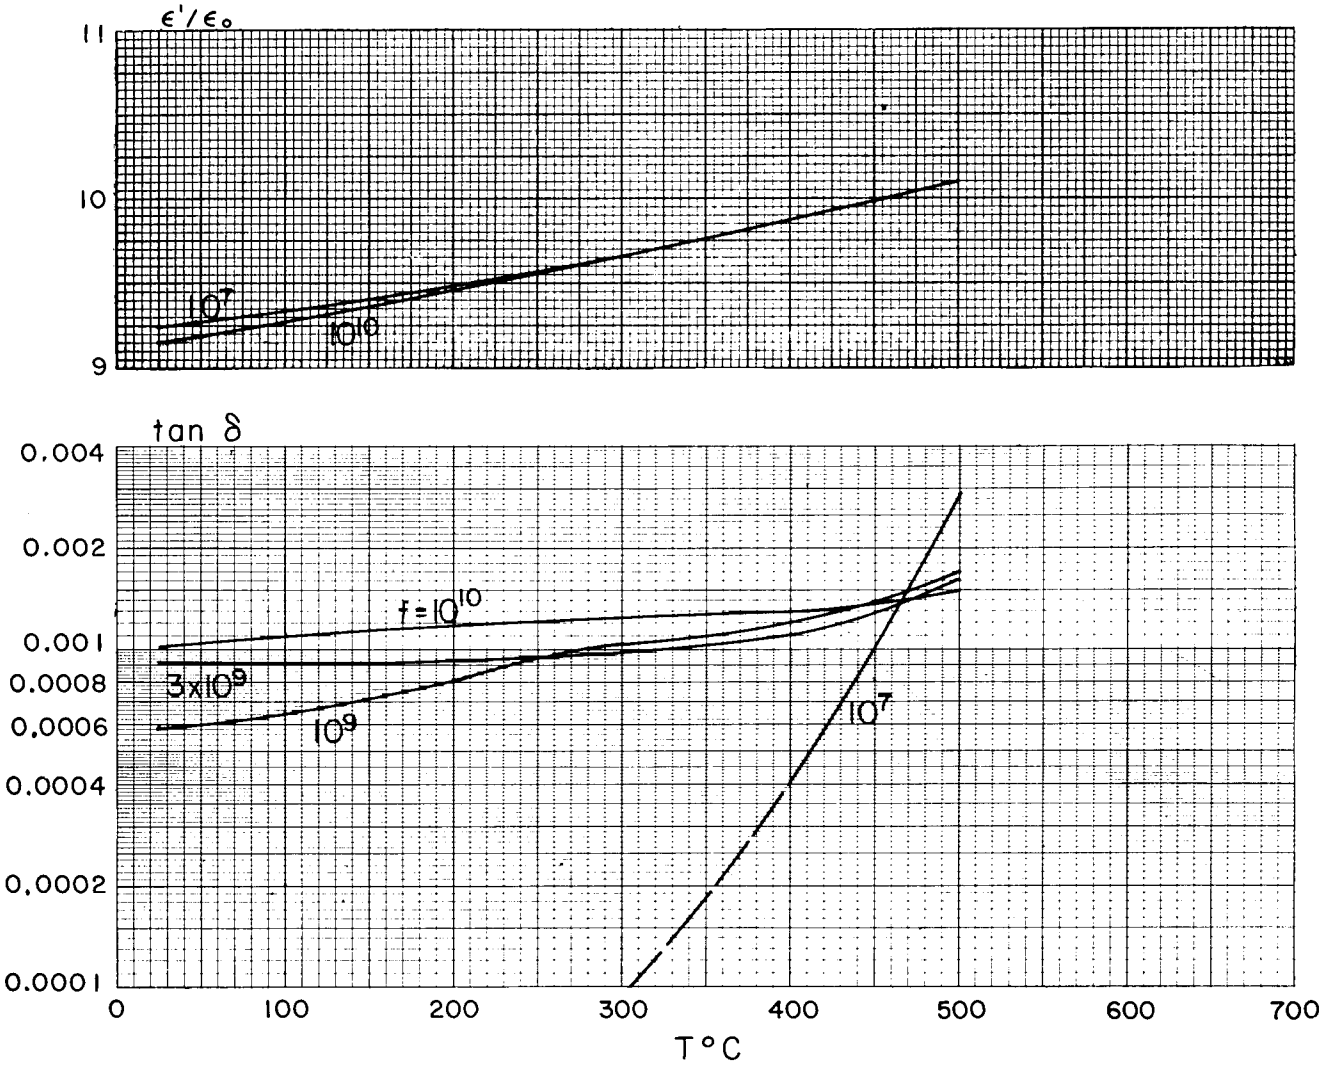

III A 2 a. Aluminas

"Diamonite" P-3142


Diamonite Products Div.
U.S. Ceramic Tile

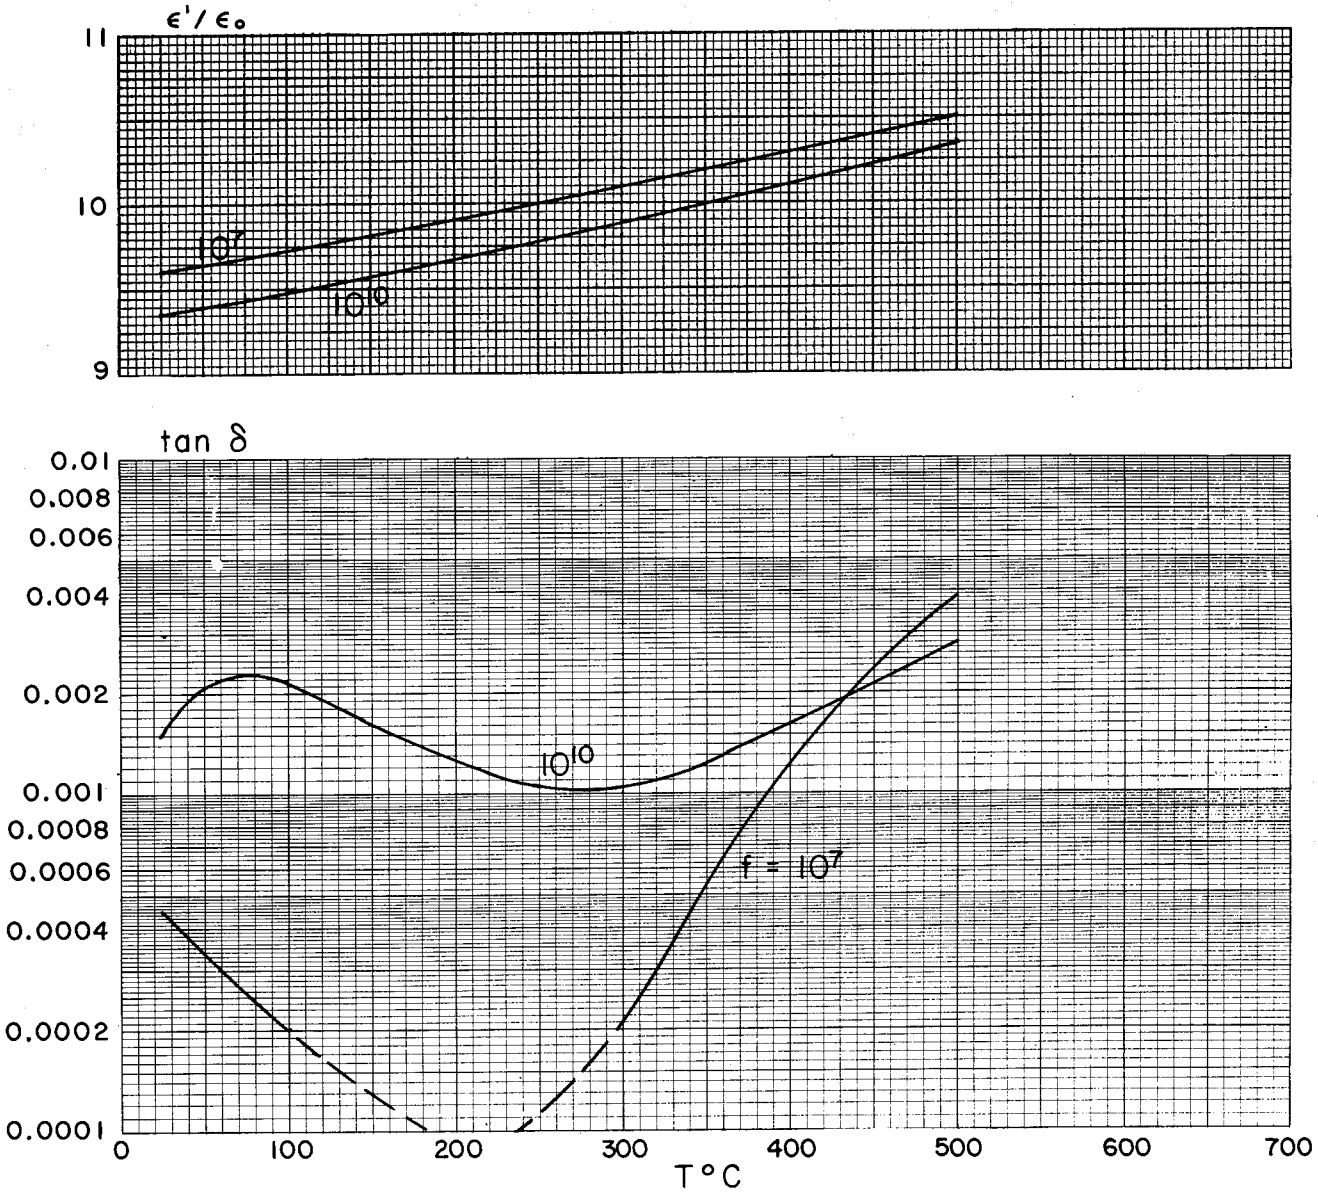

III A 2 a. Aluminas

"Diamonite" P-3459


Diamonite Products Div.
U, S. Ceramic Tile

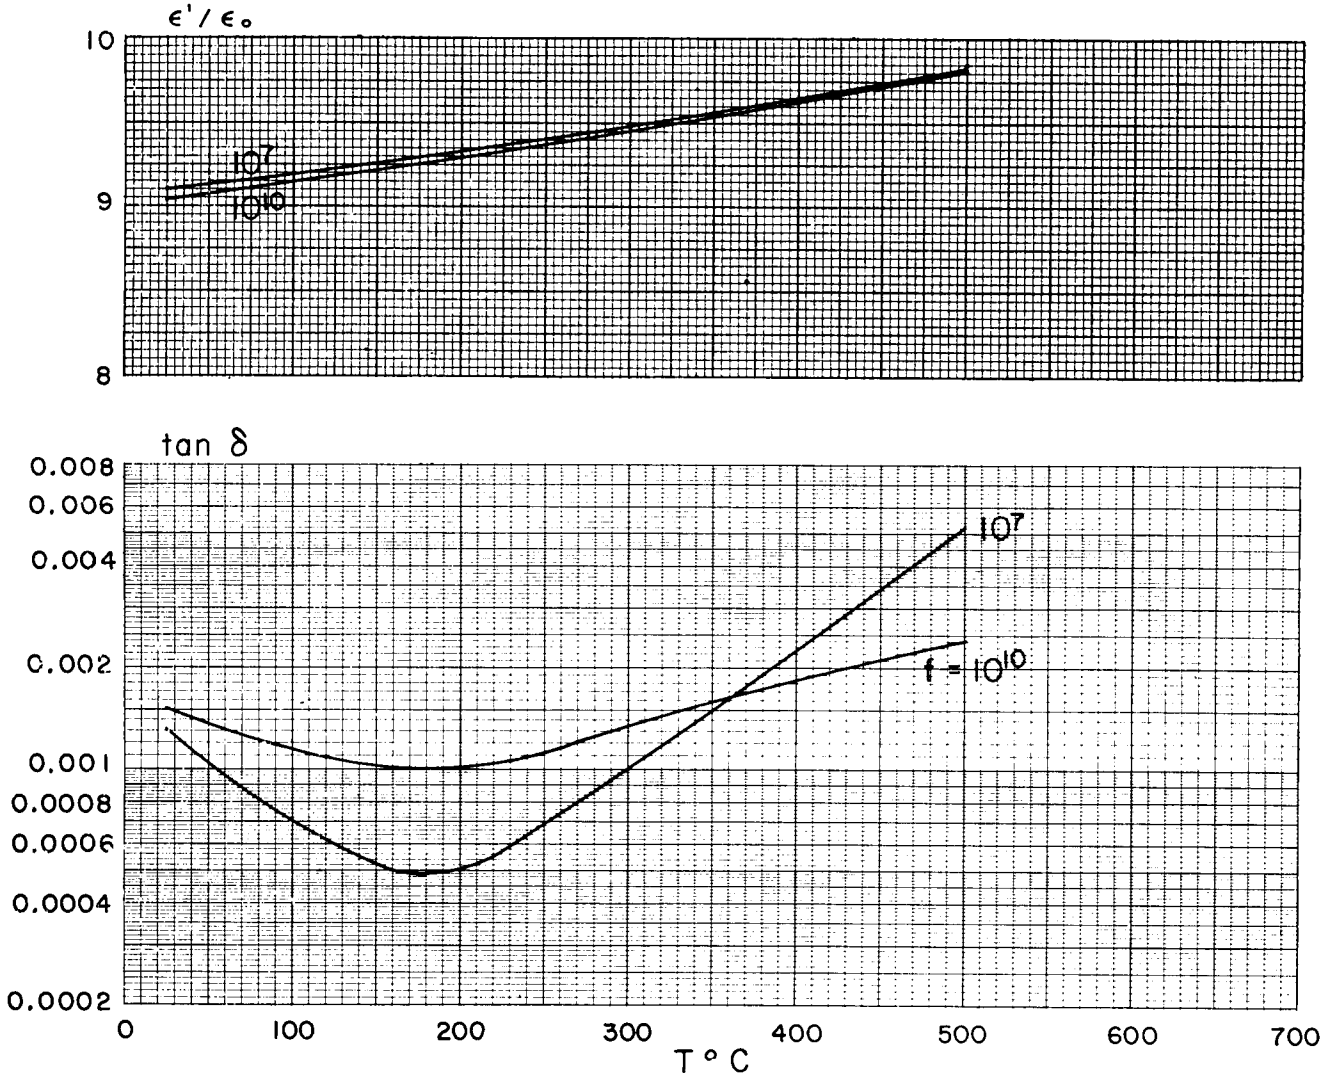

III A 2 a. Aluminas


"Diamonite" P-3530-40

Diamonite Products Div.
U.S. Ceramic Tile

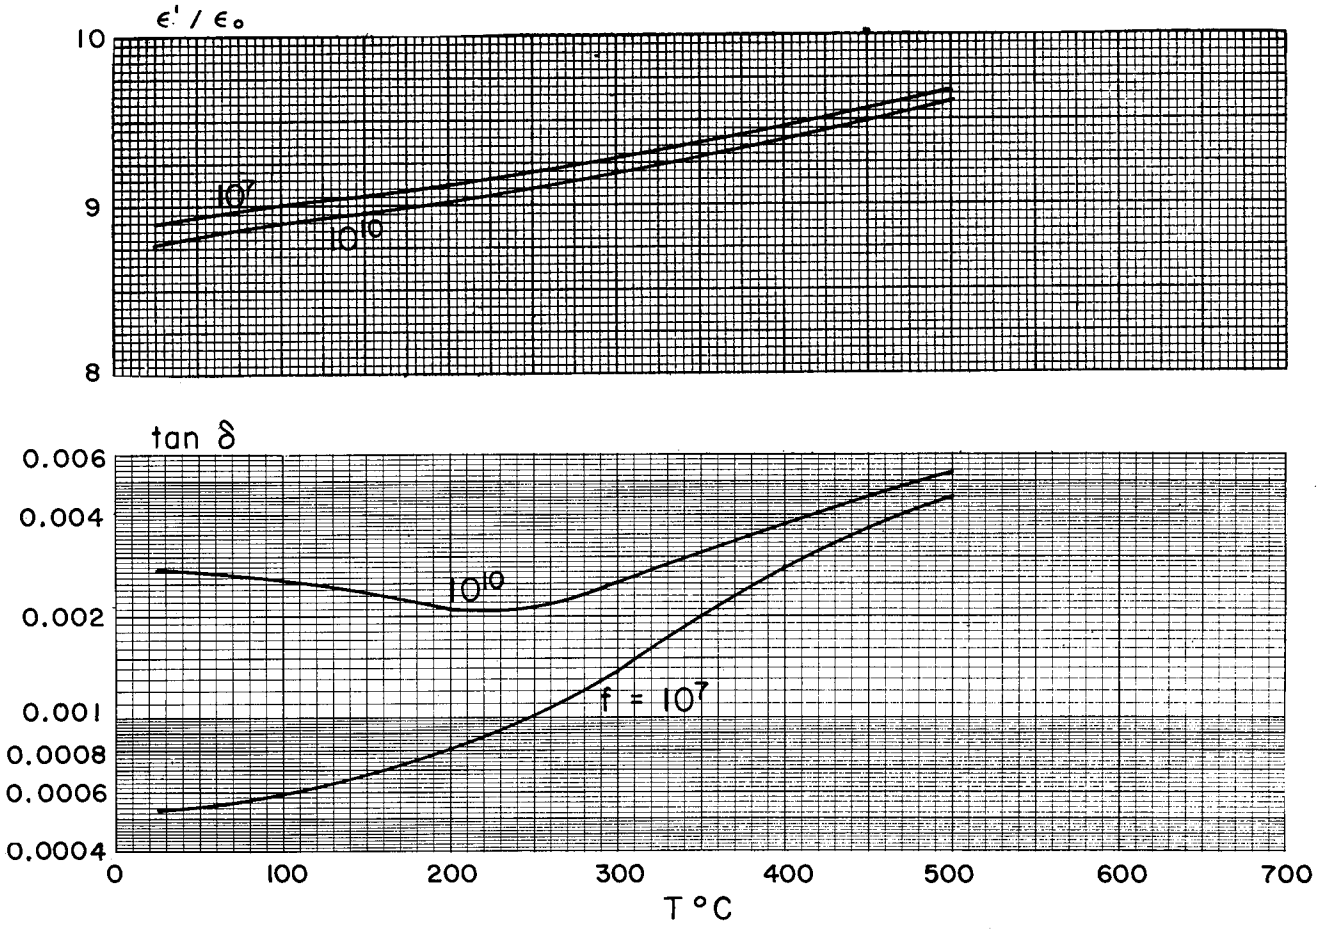


III A 2 a. Aluminas

Alumina (high purity) Kearfott

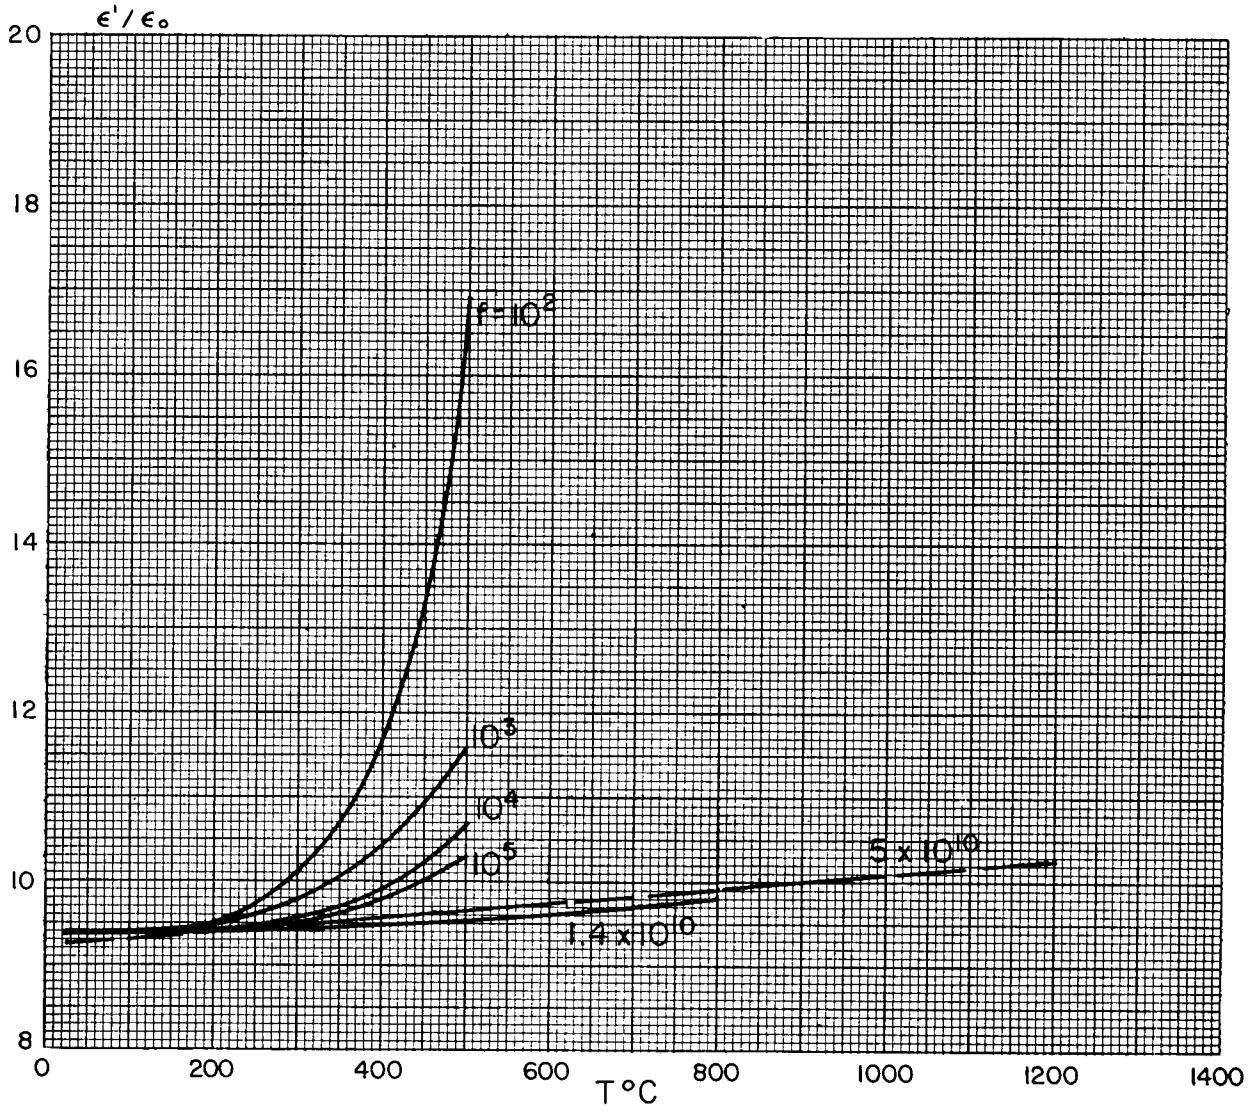

III A 2 a. Aluminas


Alumina (high purity) Kearfott

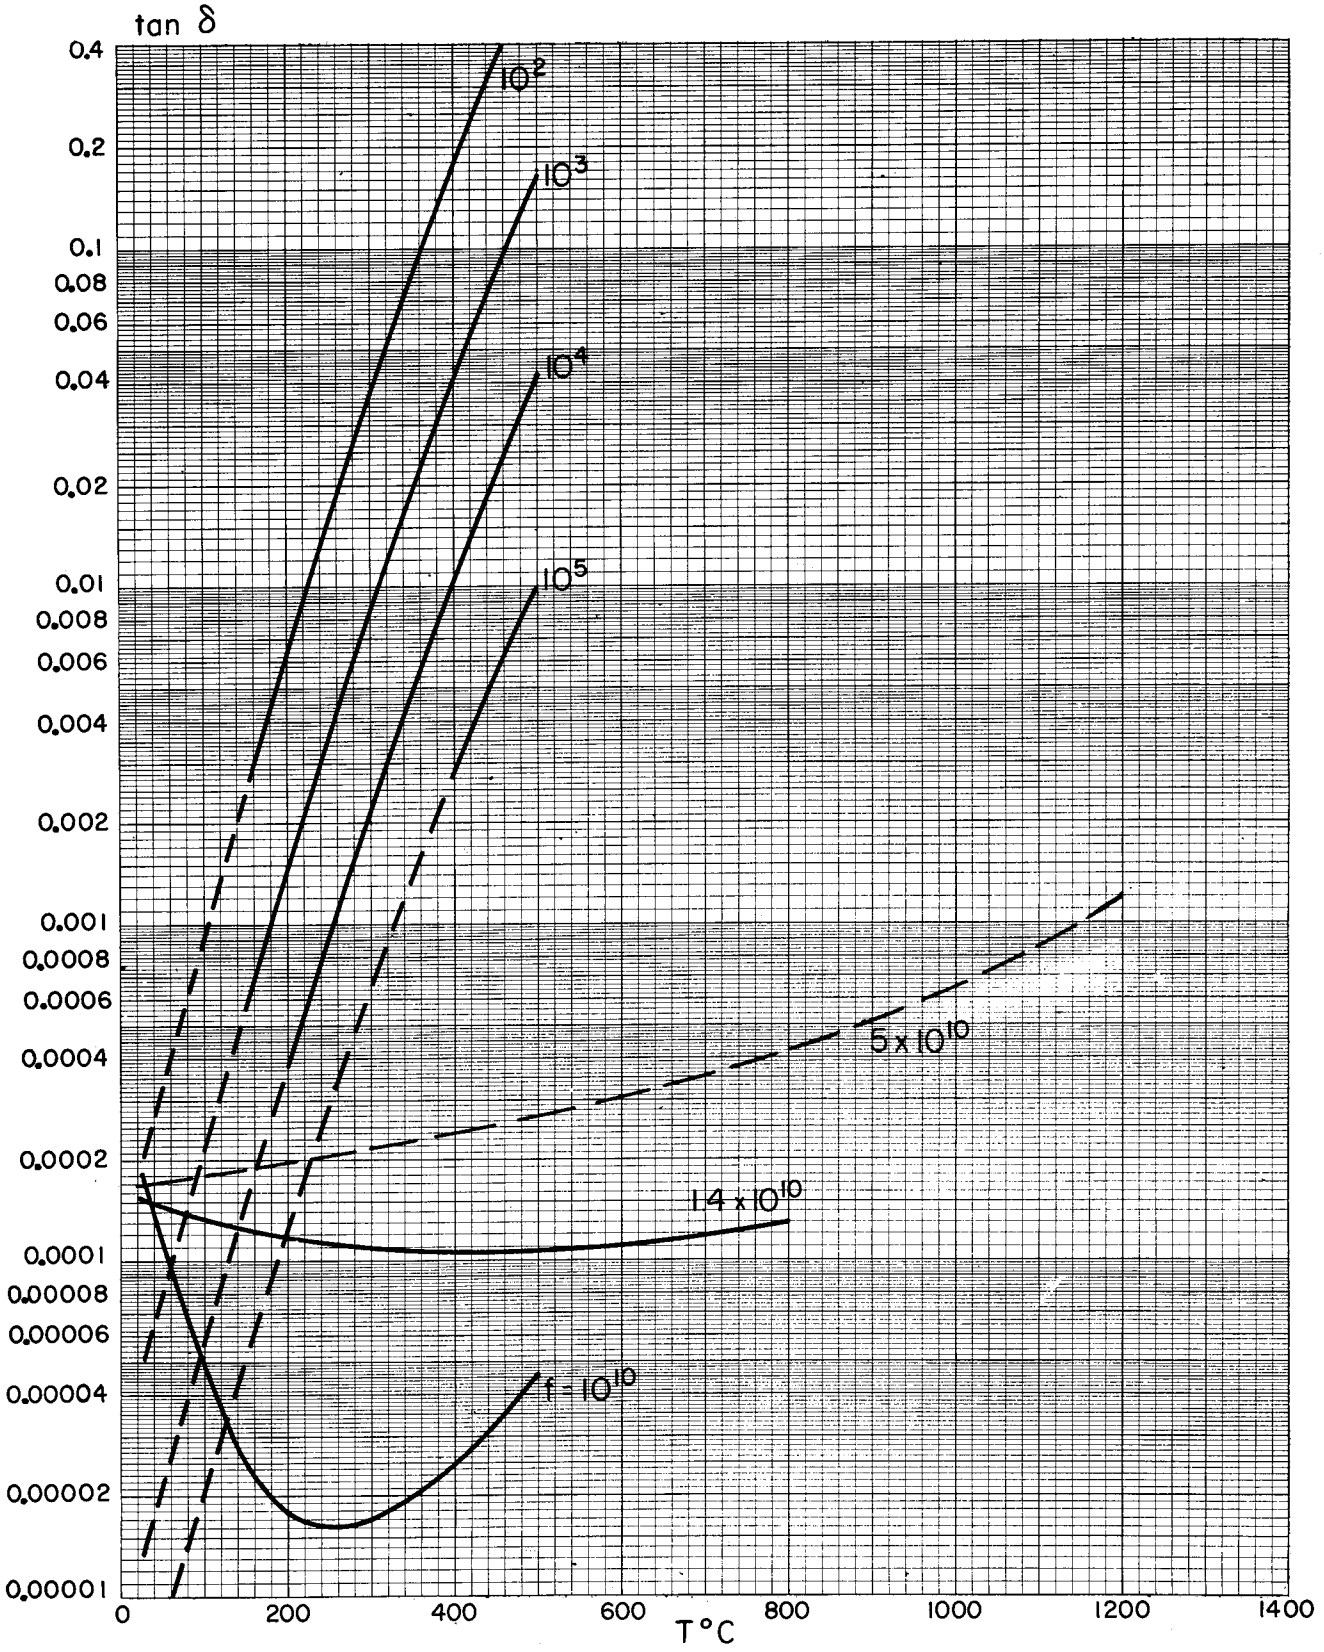

III A 2 a. Aluminas


Frenchtown 4462

Frenchtown

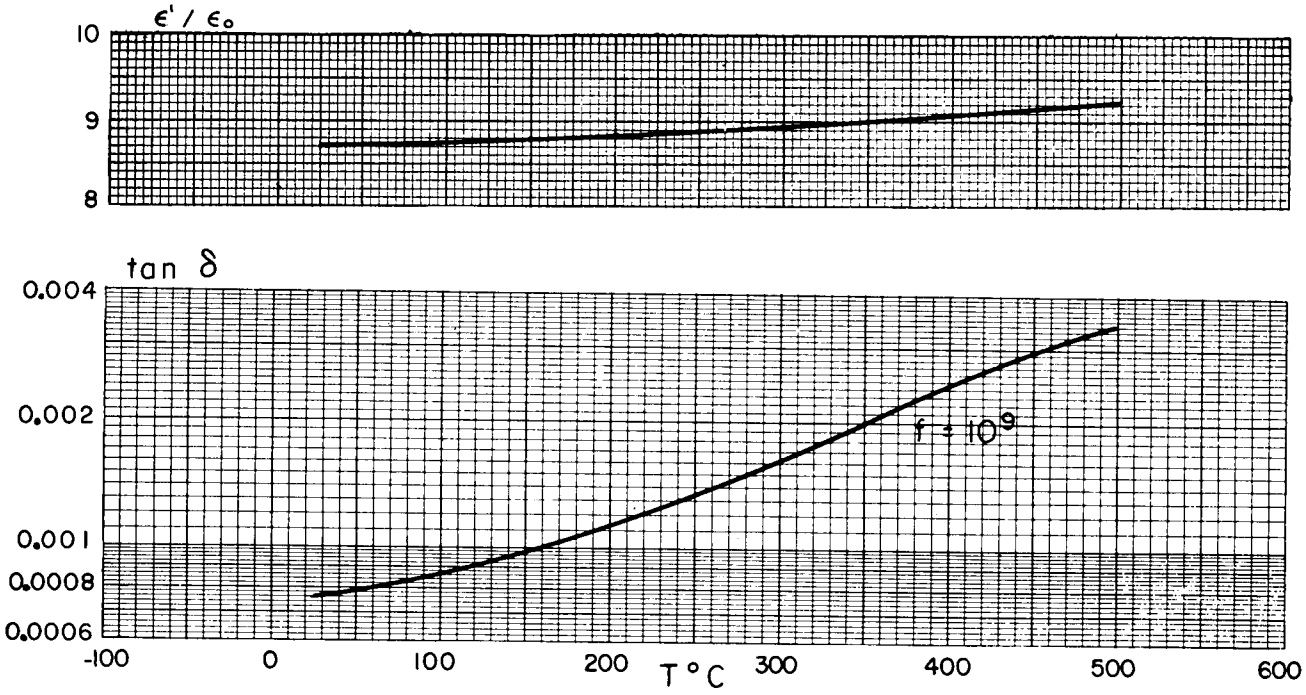


Frenchtown 6096

Frenchtown

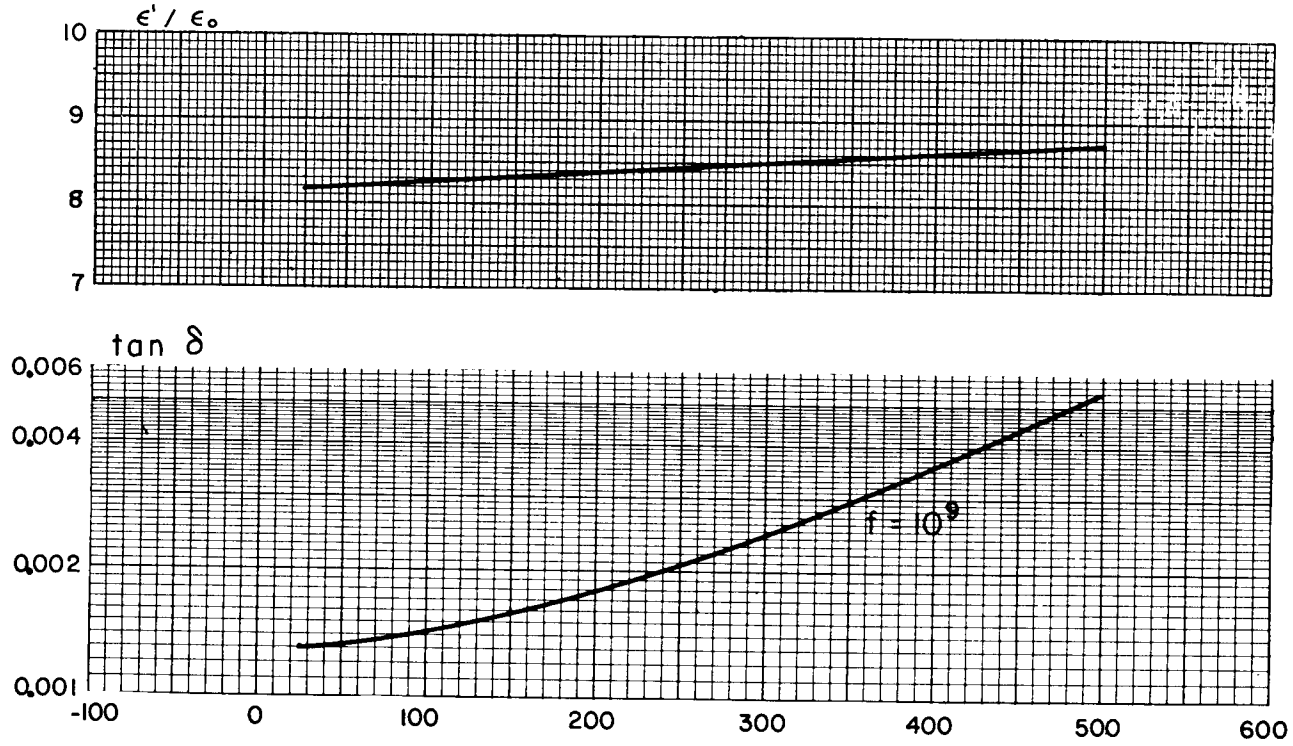


III A 2 a. Aluminas

Frenchtown 7873 Frenchtown

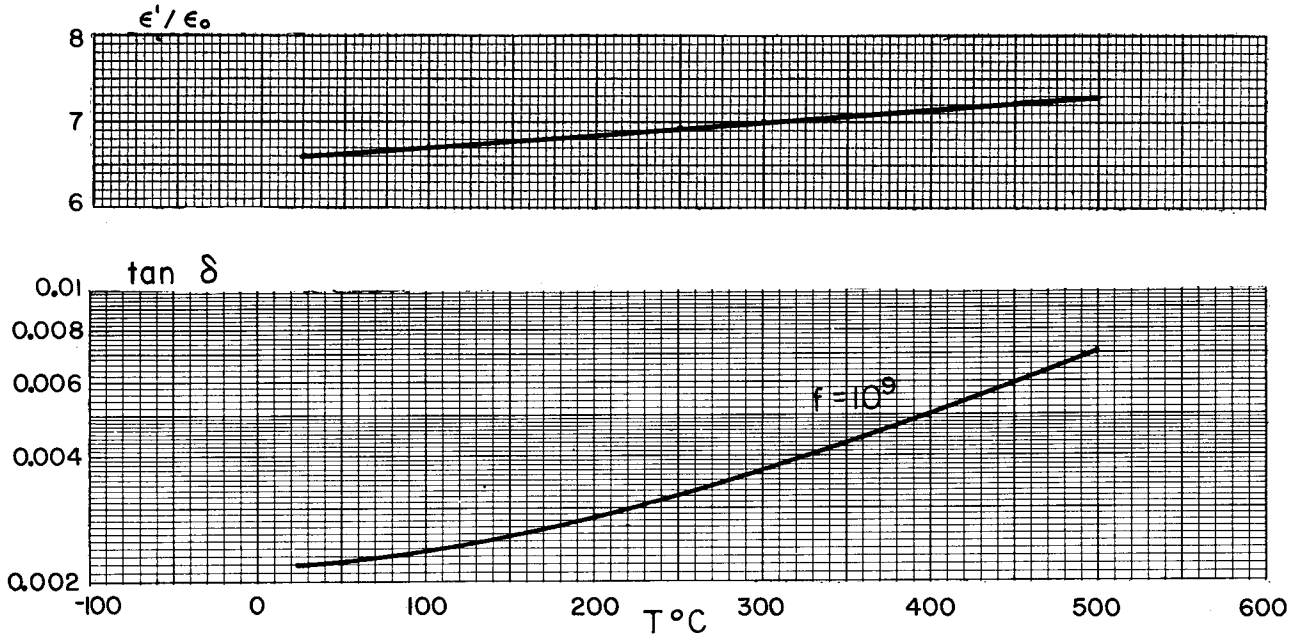


Alumina 7X Norton

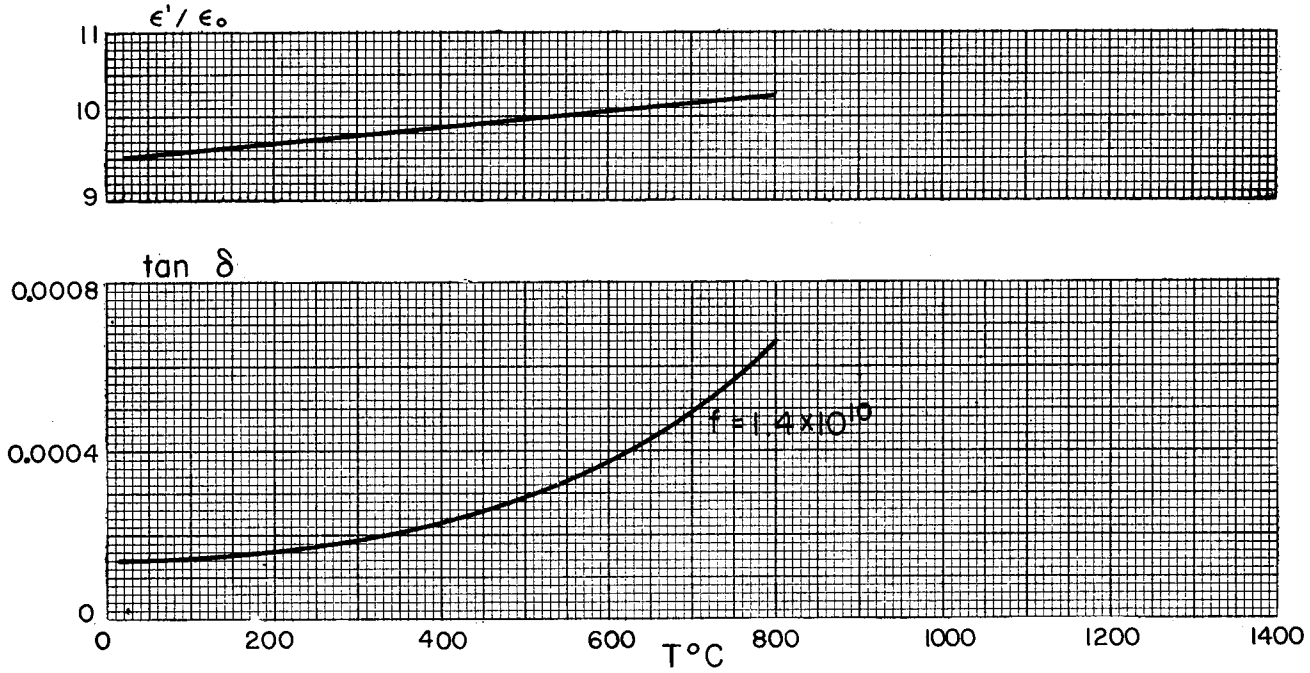

III A 2 a. Aluminas

Stupakoff 1540, 1542P, and 1550


Stupakoff

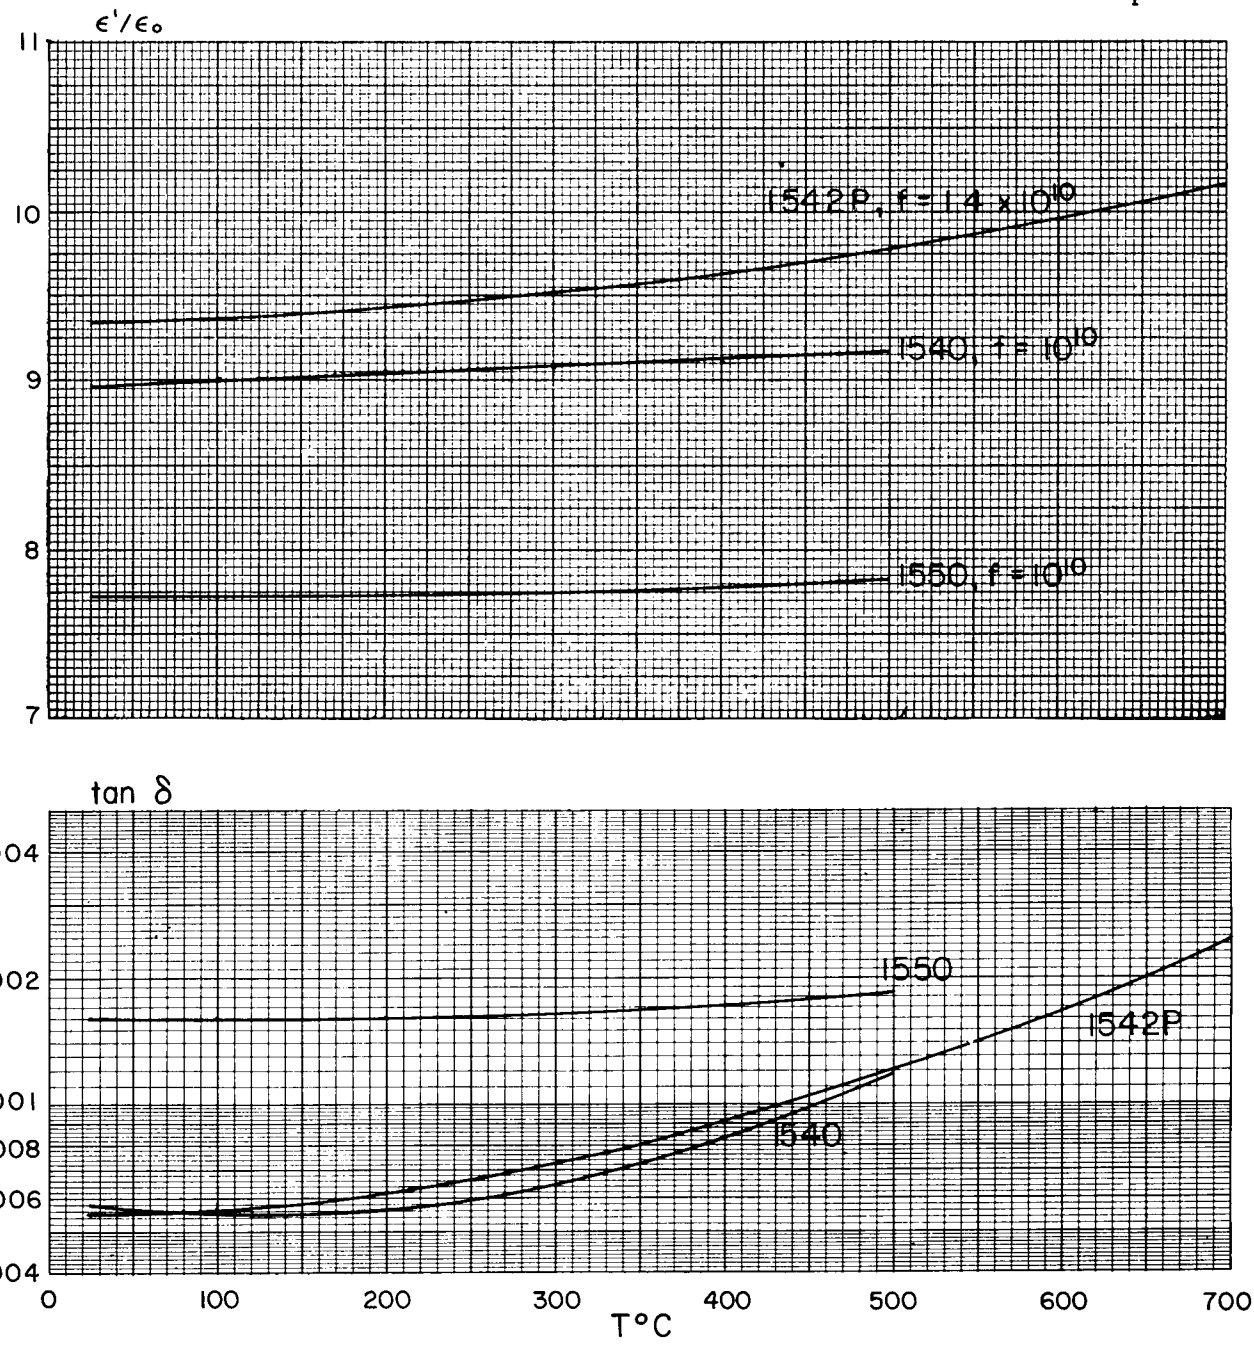

III A 2 a. Aluminas


Stupakoff 1510

Stupakoff

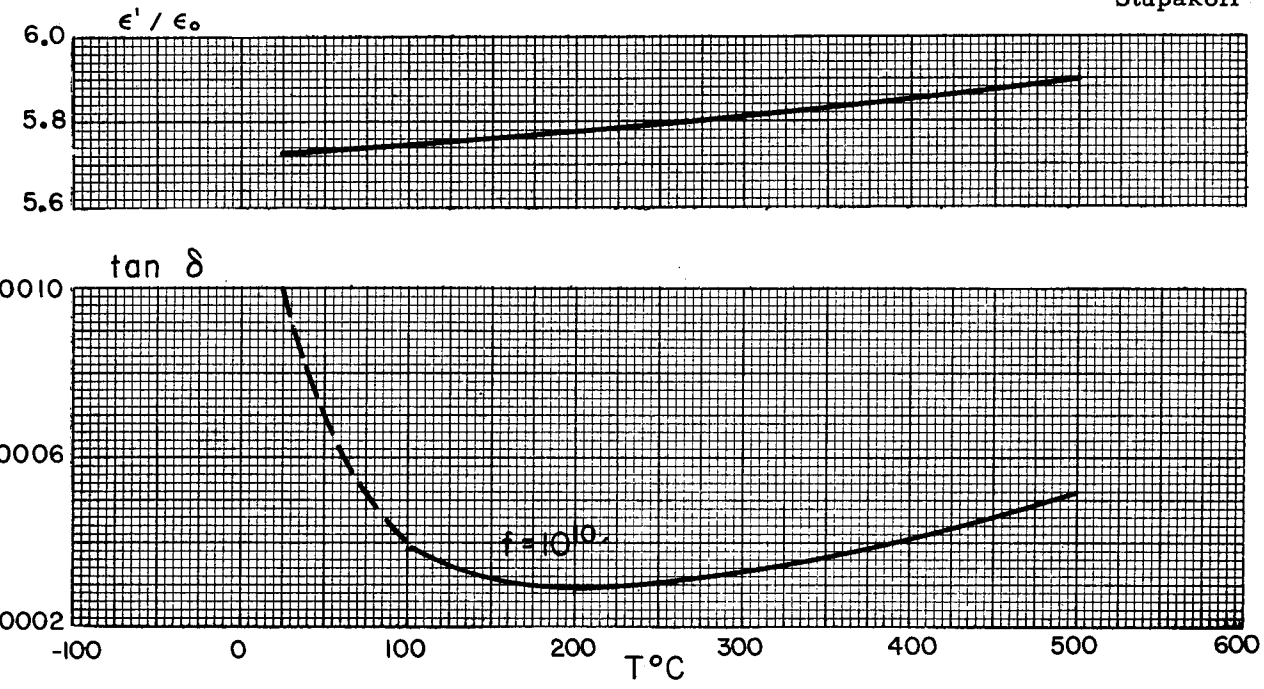


"Alite" AP 312

U.S. Stoneware

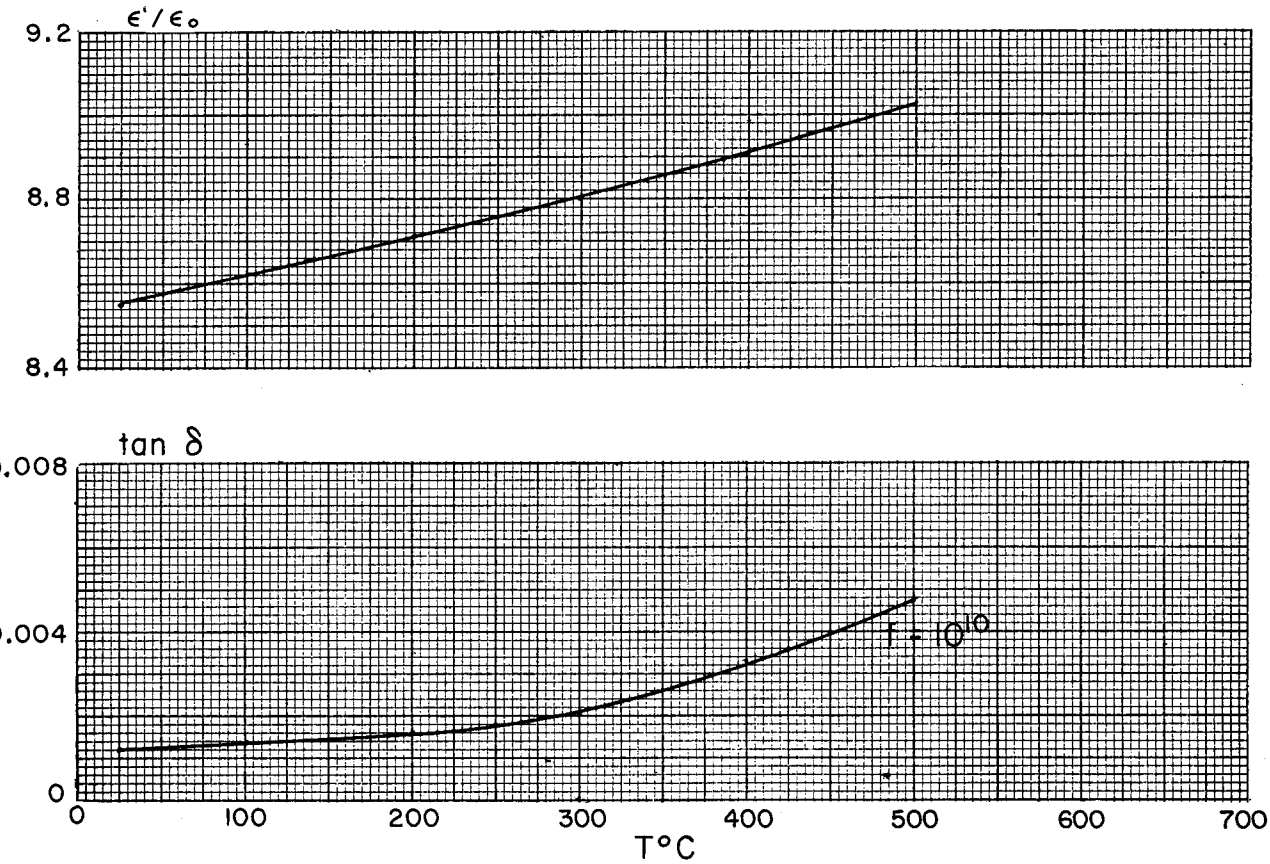


III A 2 a. Aluminas

"Wesgo" AL-300 Western Gold and Platinum

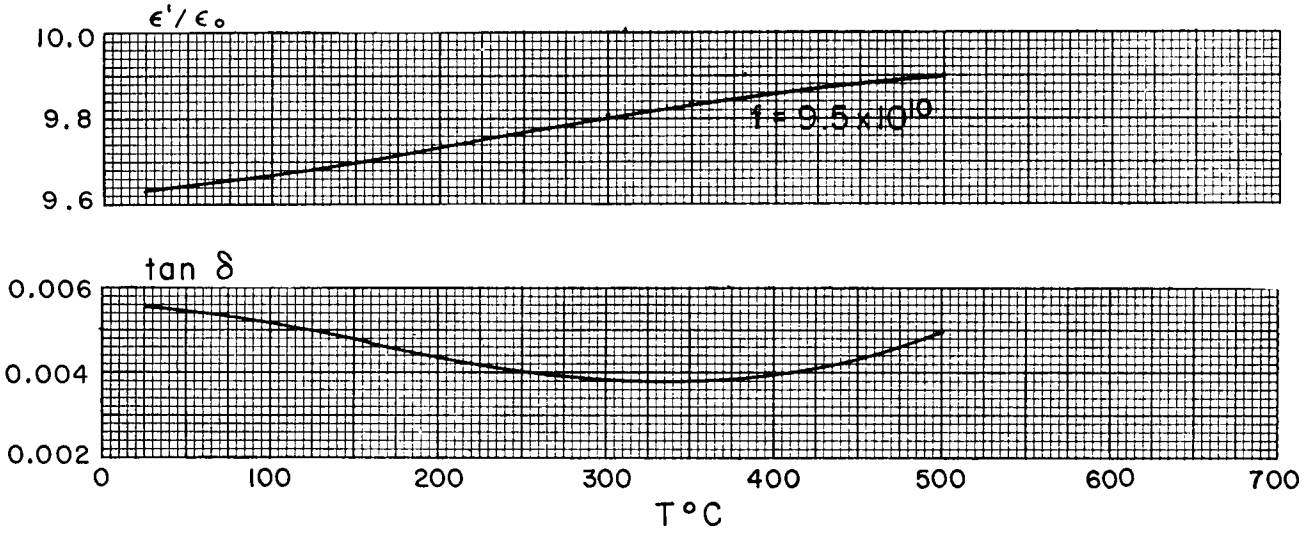


III A 2 b. Beryllias

Beryllium oxide, crucible grade Beryllium Corp.

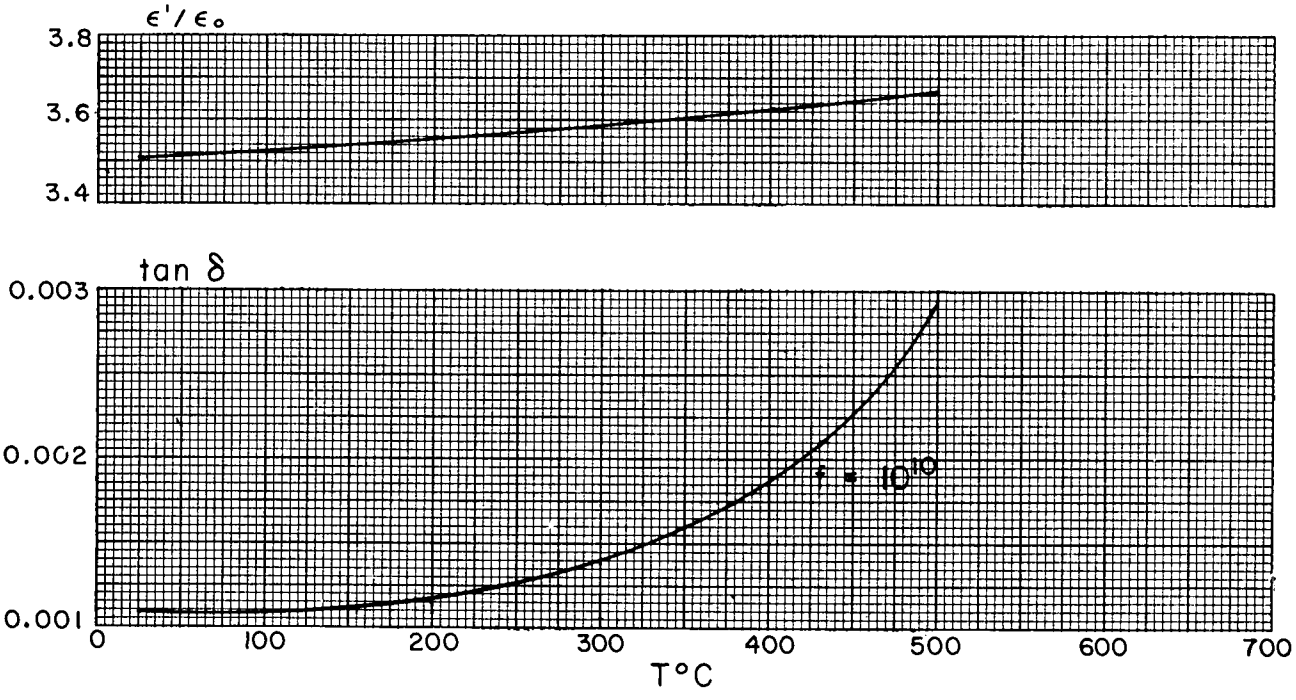


III A 2 b. Beryllias

Beryllium oxide, hot pressed — Beryllium Corp.

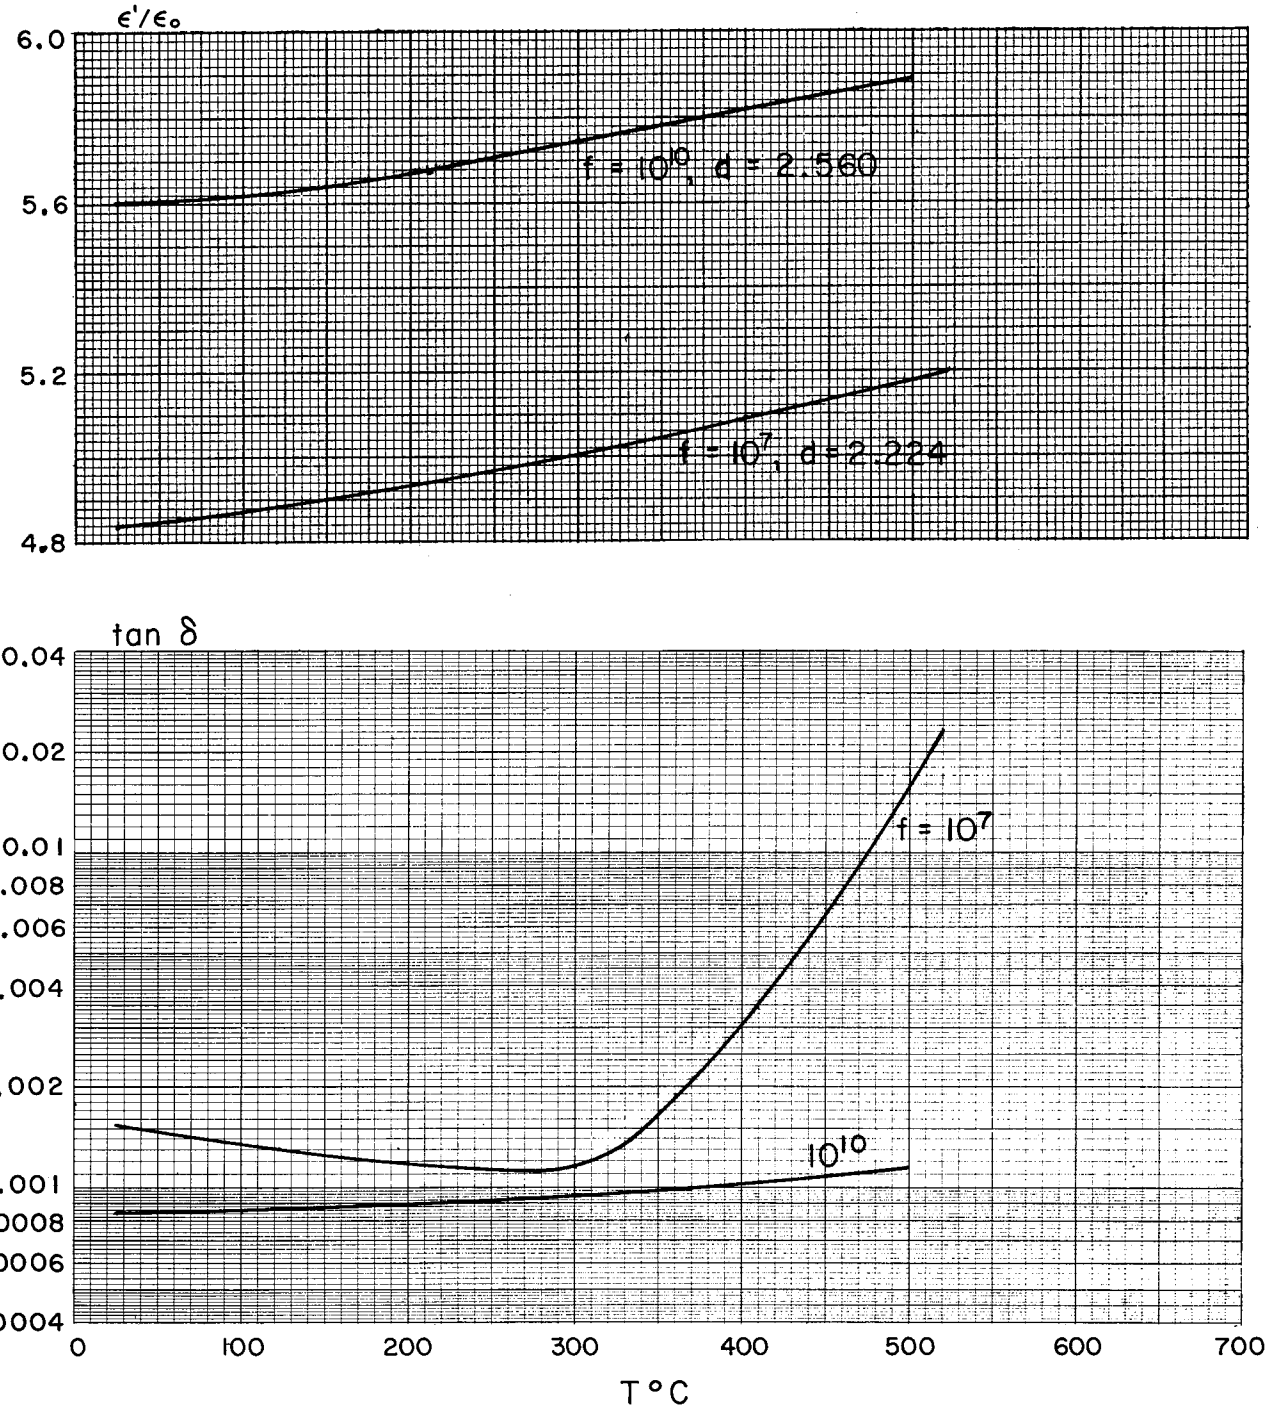


III A 2 c. Ferrites

Magnesium Manganite — General Ceramics

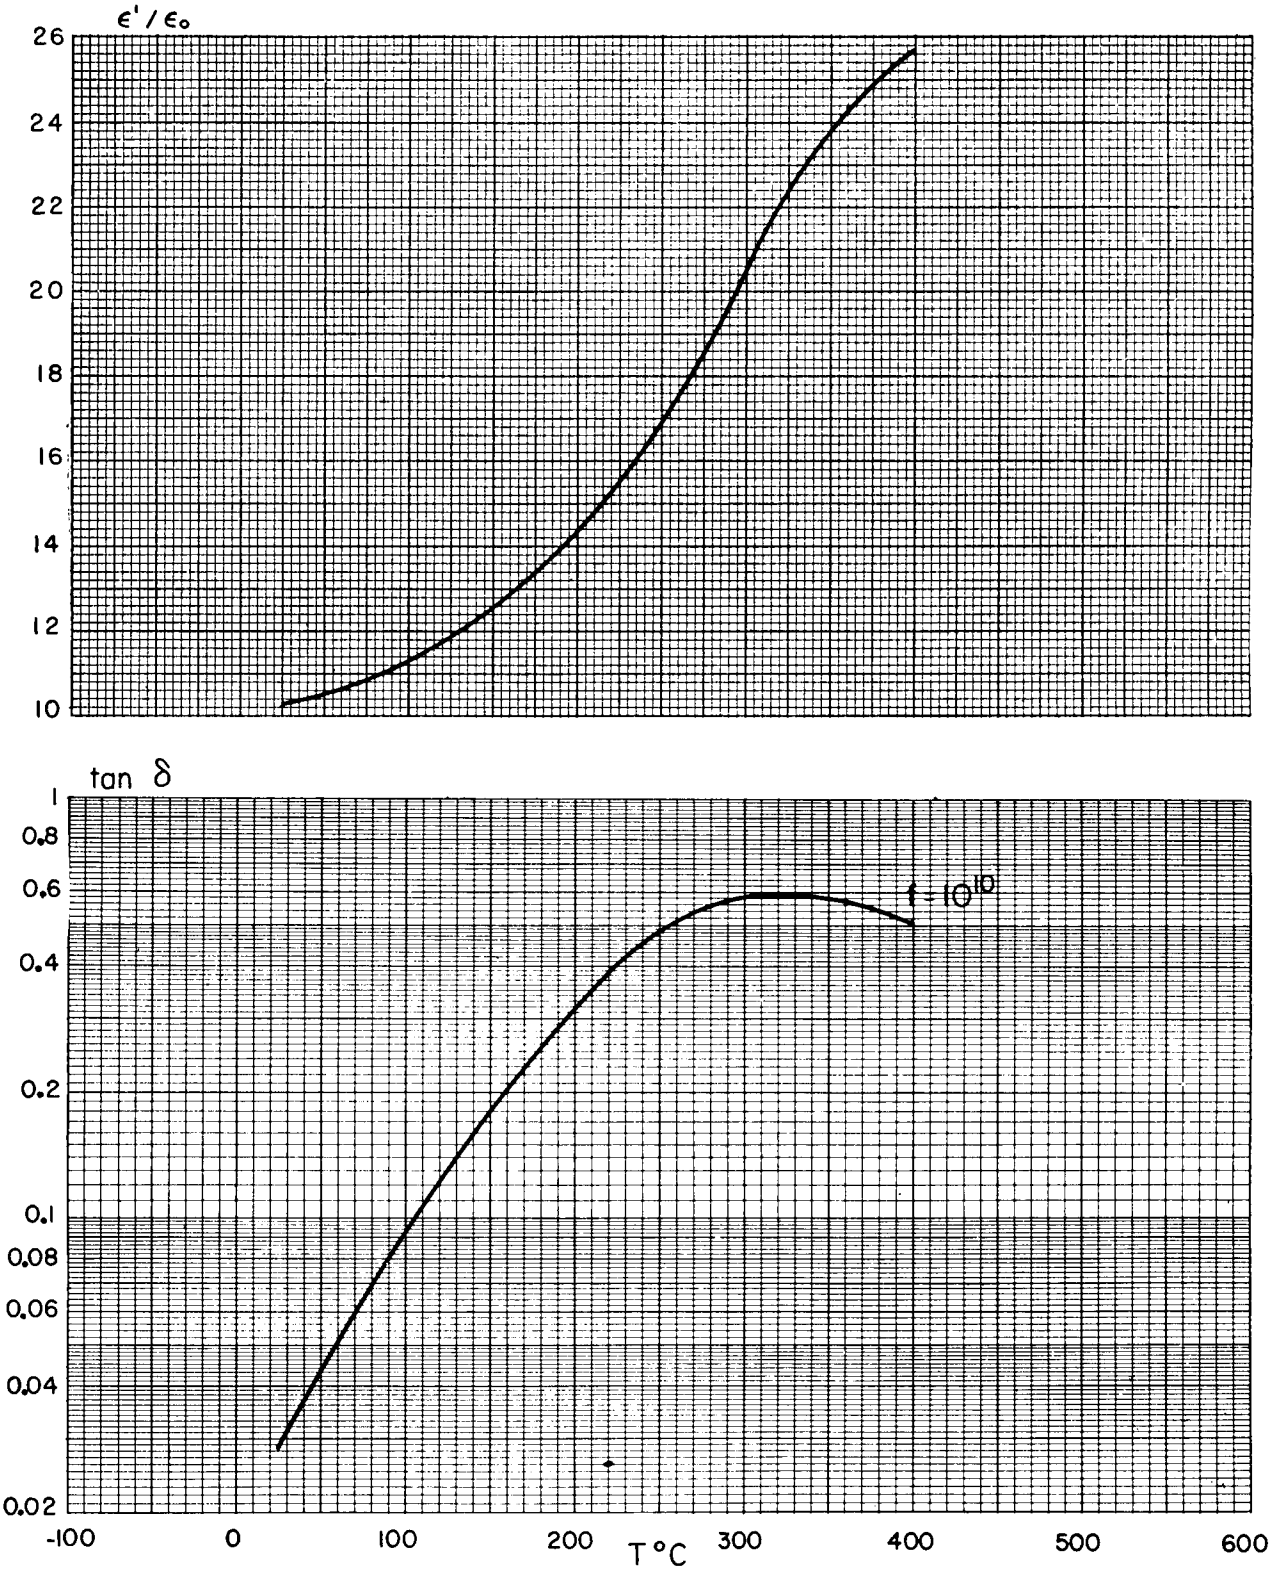


III A 2 d. Steatite

Ceramic BN 3054 — General Ceramics

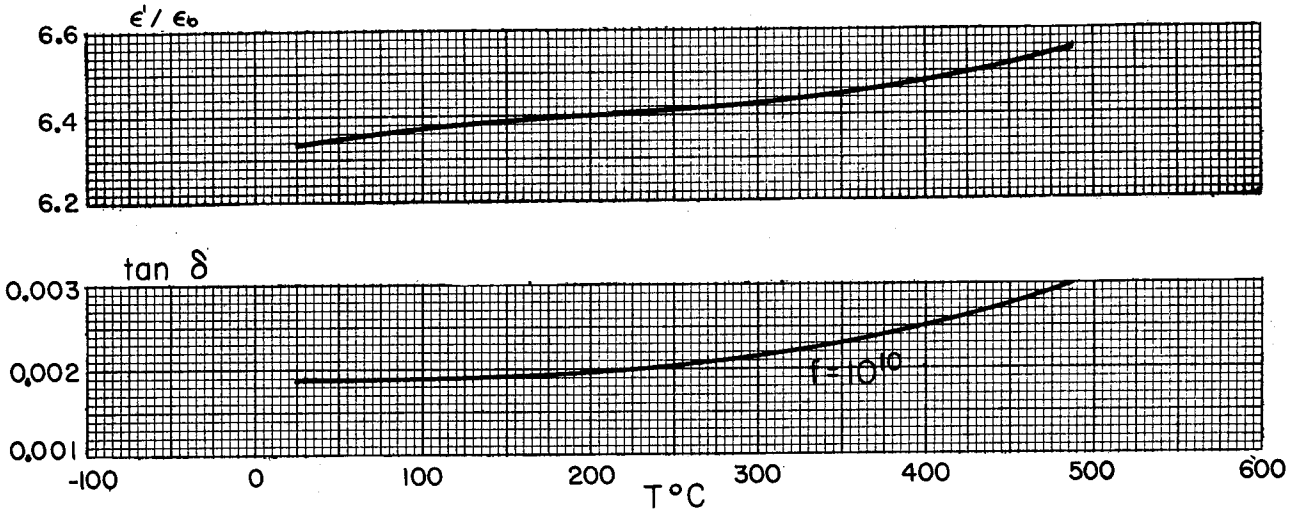


Steatite body 7292 — General Ceramics

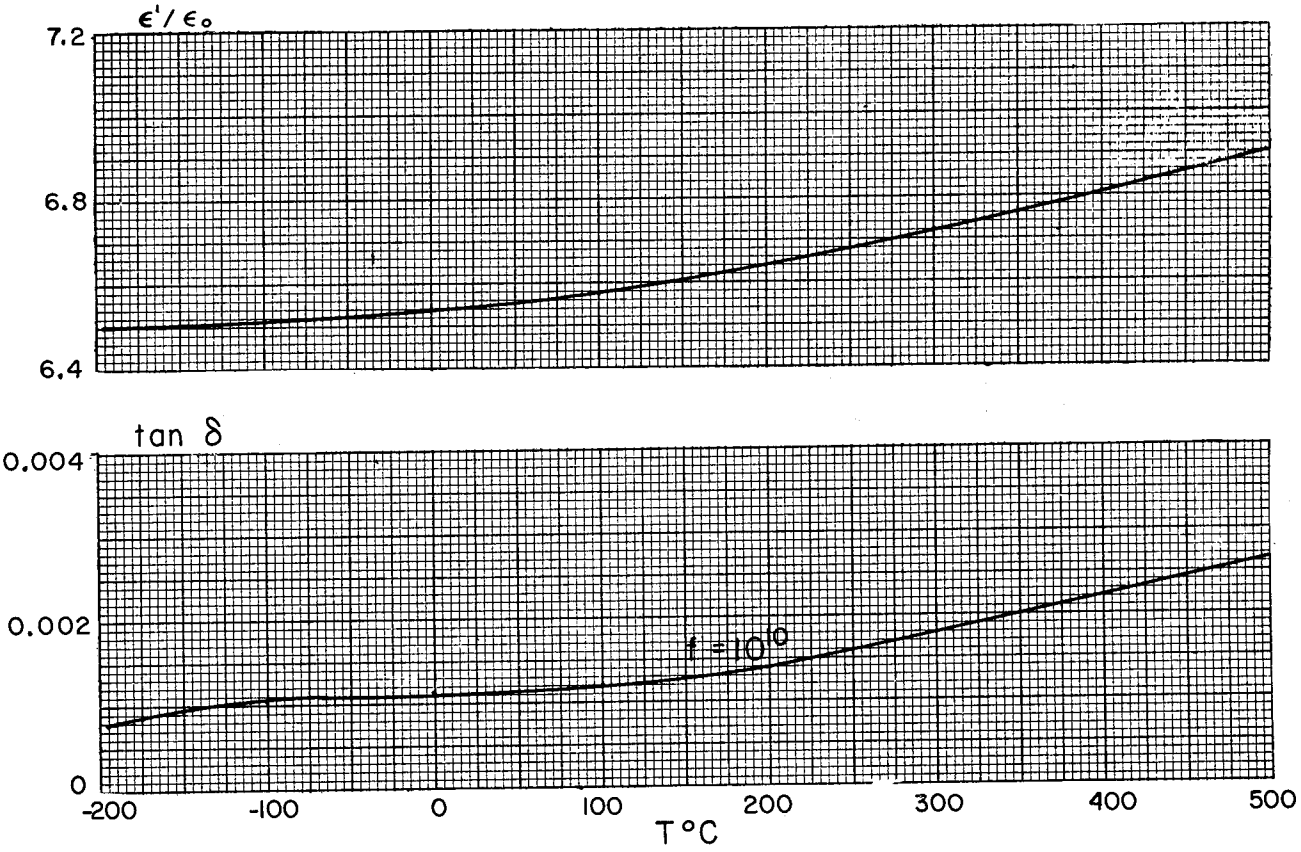

III A 2 d. Steatite


Ceramic F-66

Bell Telephone Labs.

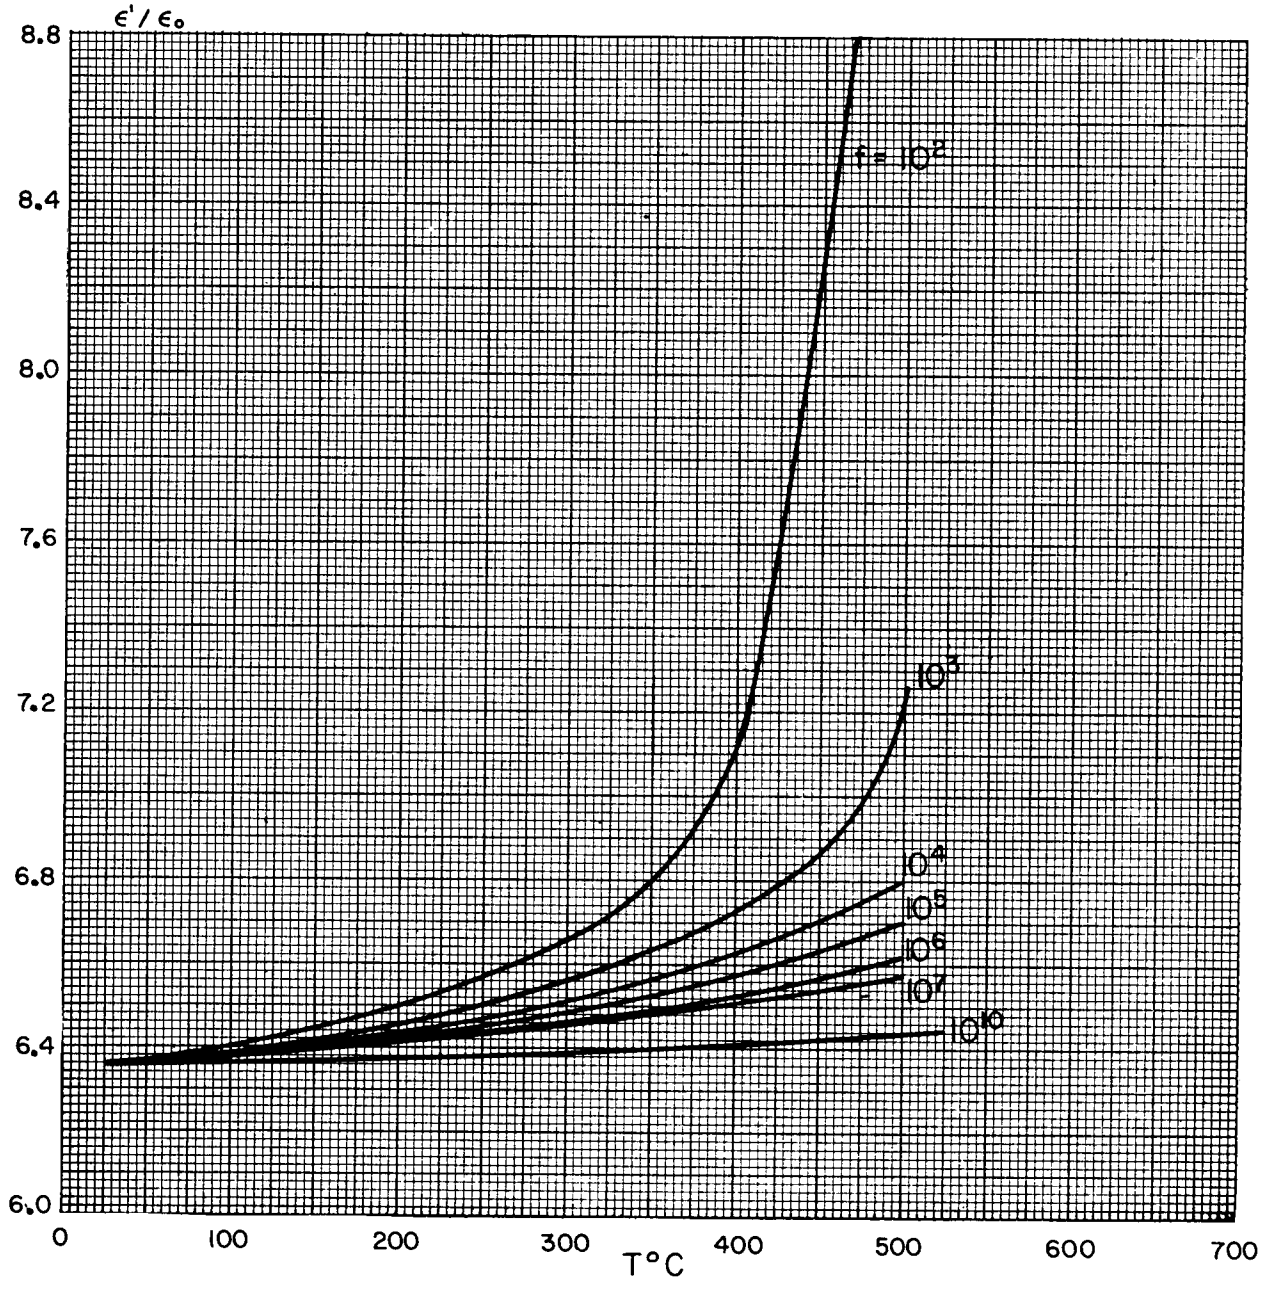

III A 2 d. Steatite


Ceramic F-66 Bell Telephone Labs.

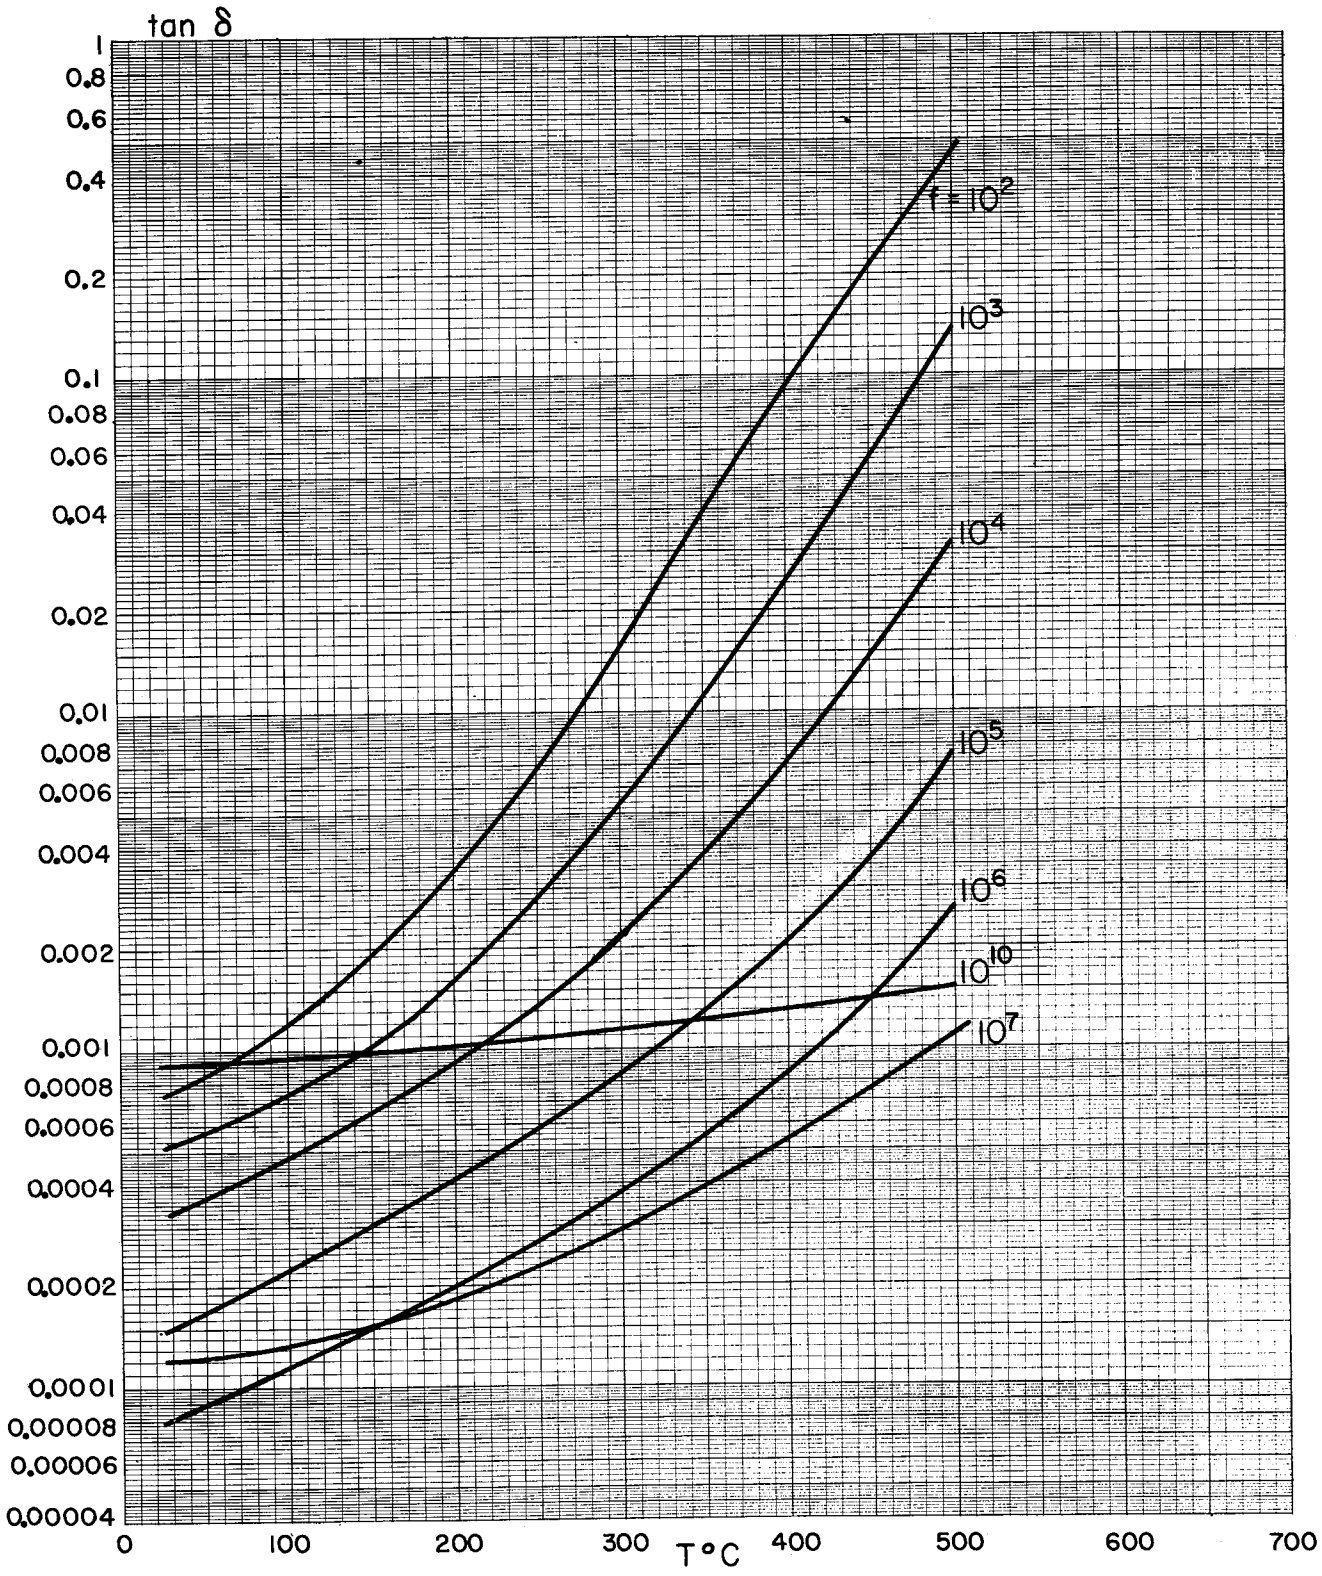

III A 2 e. Wollastonite


"AlSiMag" 577

American Lava

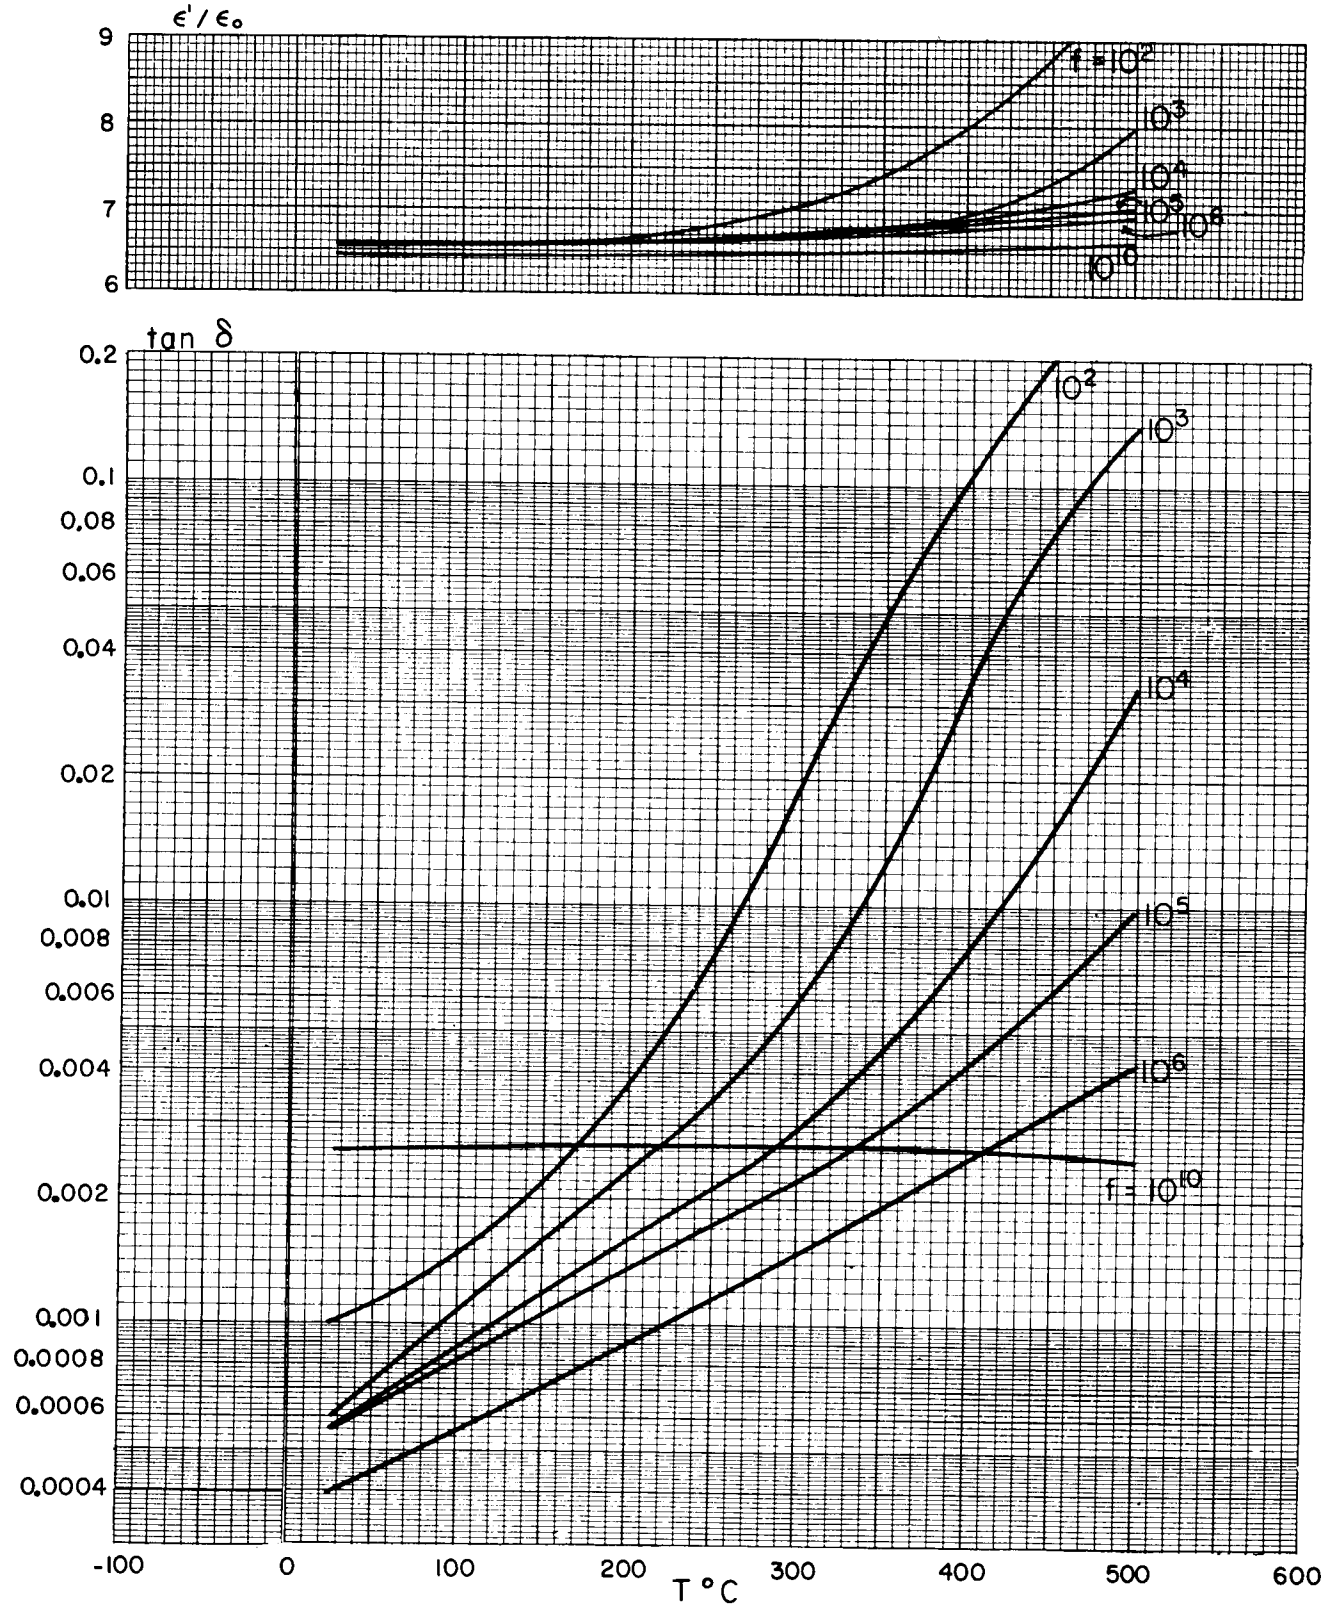


III A 2 f. Zircons

"AlSiMag" 475 (density 3.43 gm/cc) American Lava

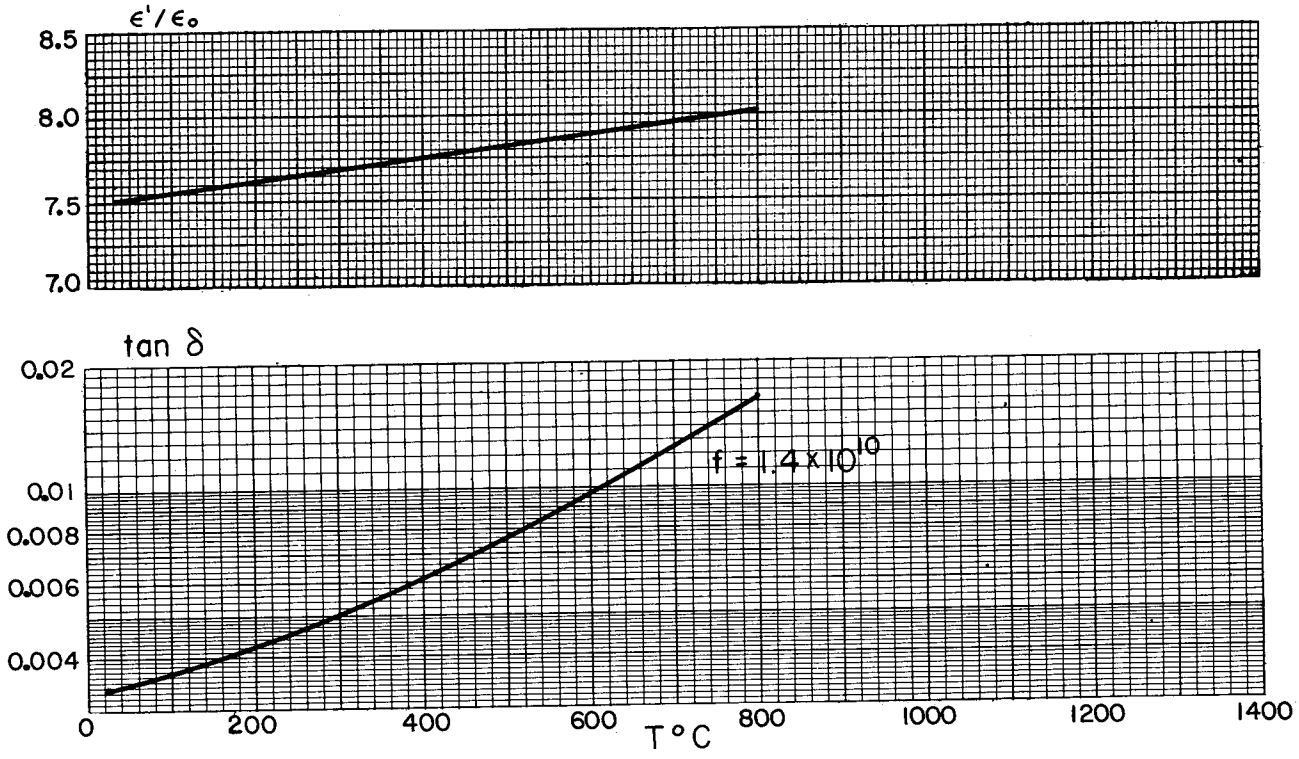


III A 2 f. Zircons

"AlSiMag" 475 (density 3.69 gm/cc) American Lava

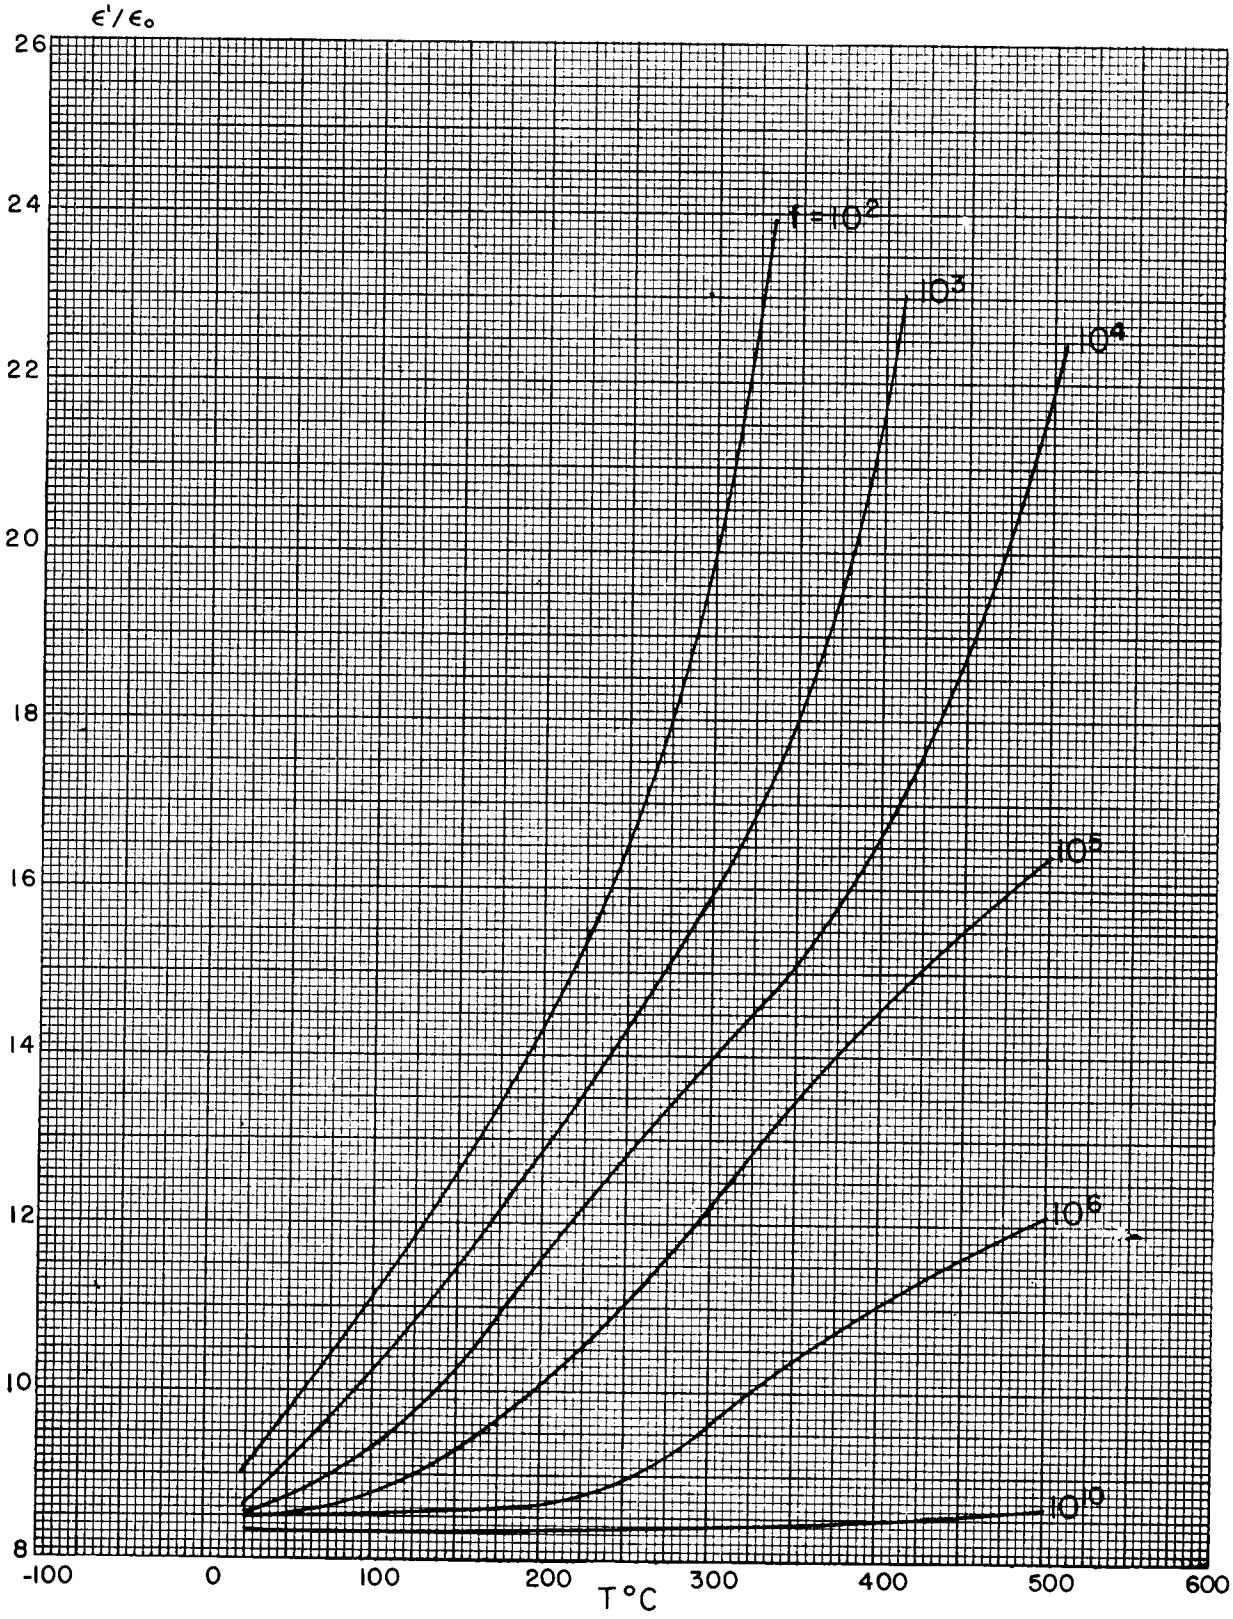


III A 2 f. Zircons

"AlSiMag" 475 (density 3.69 gm/cc) American Lava

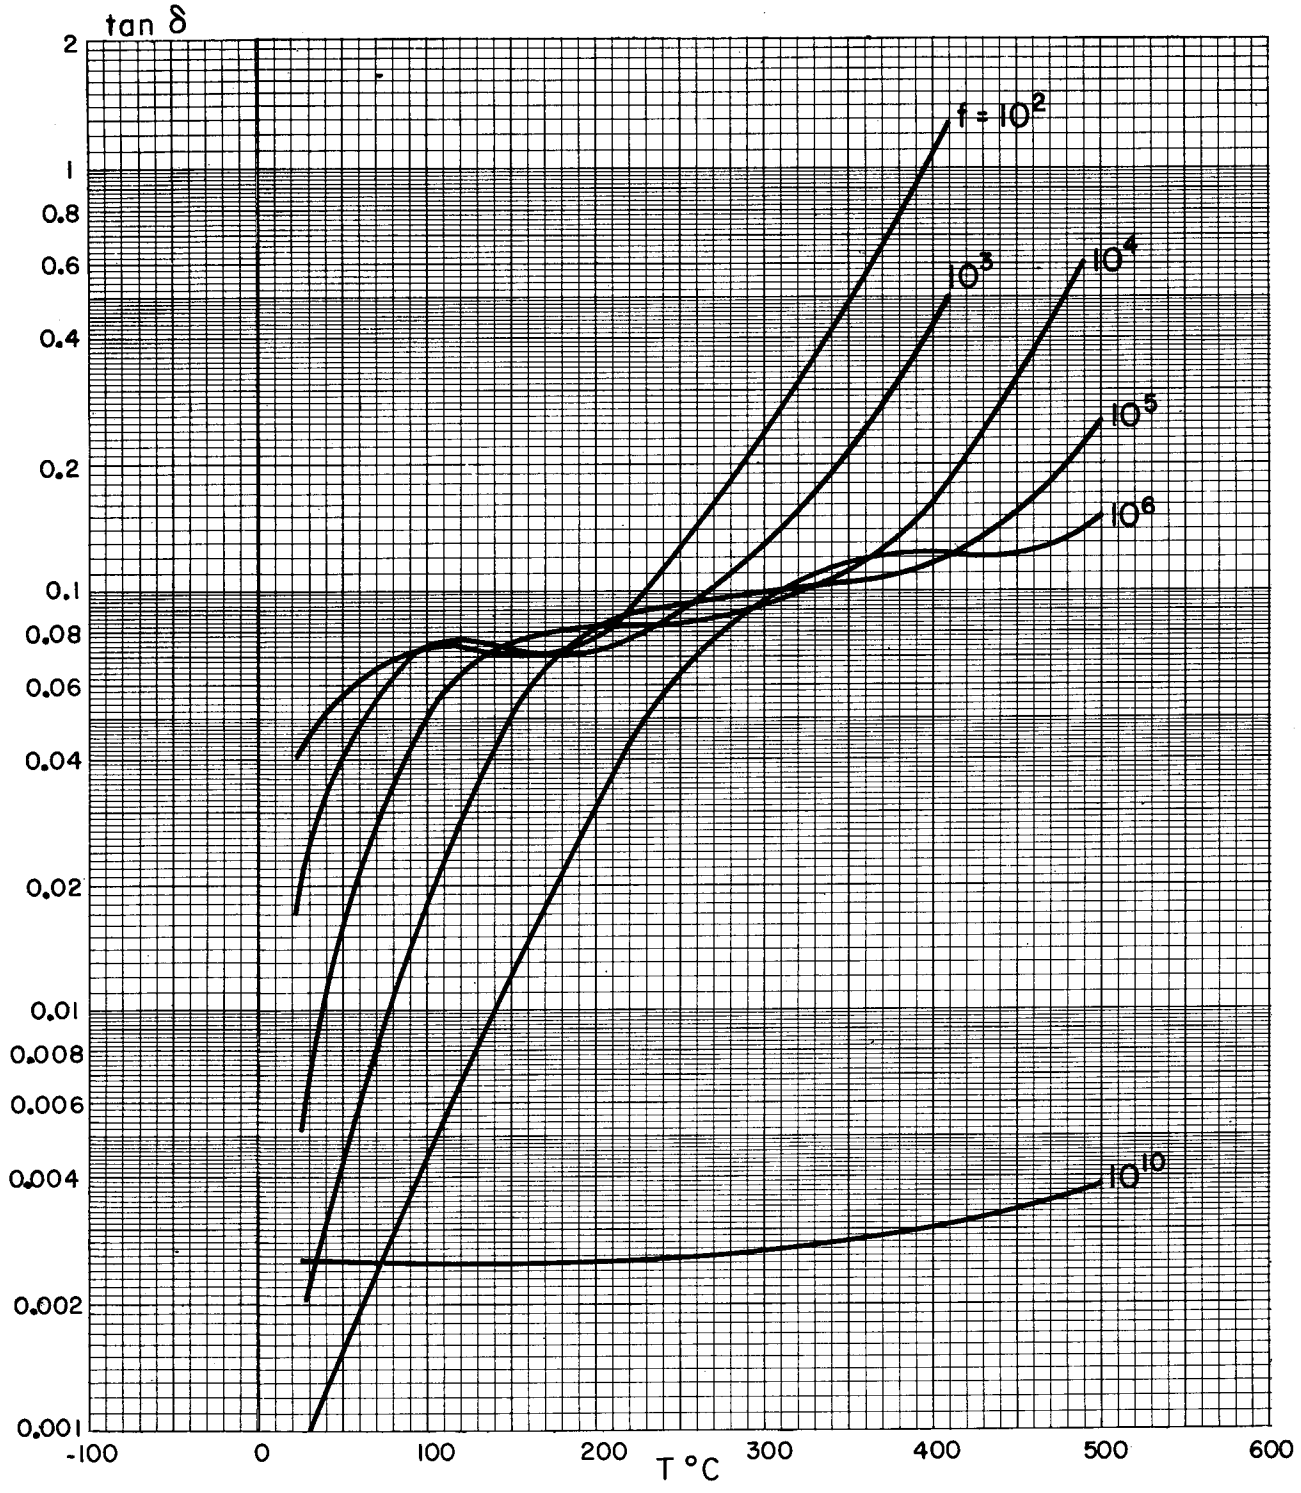


III A 3. Glasses

Corning glass 7070 Corning

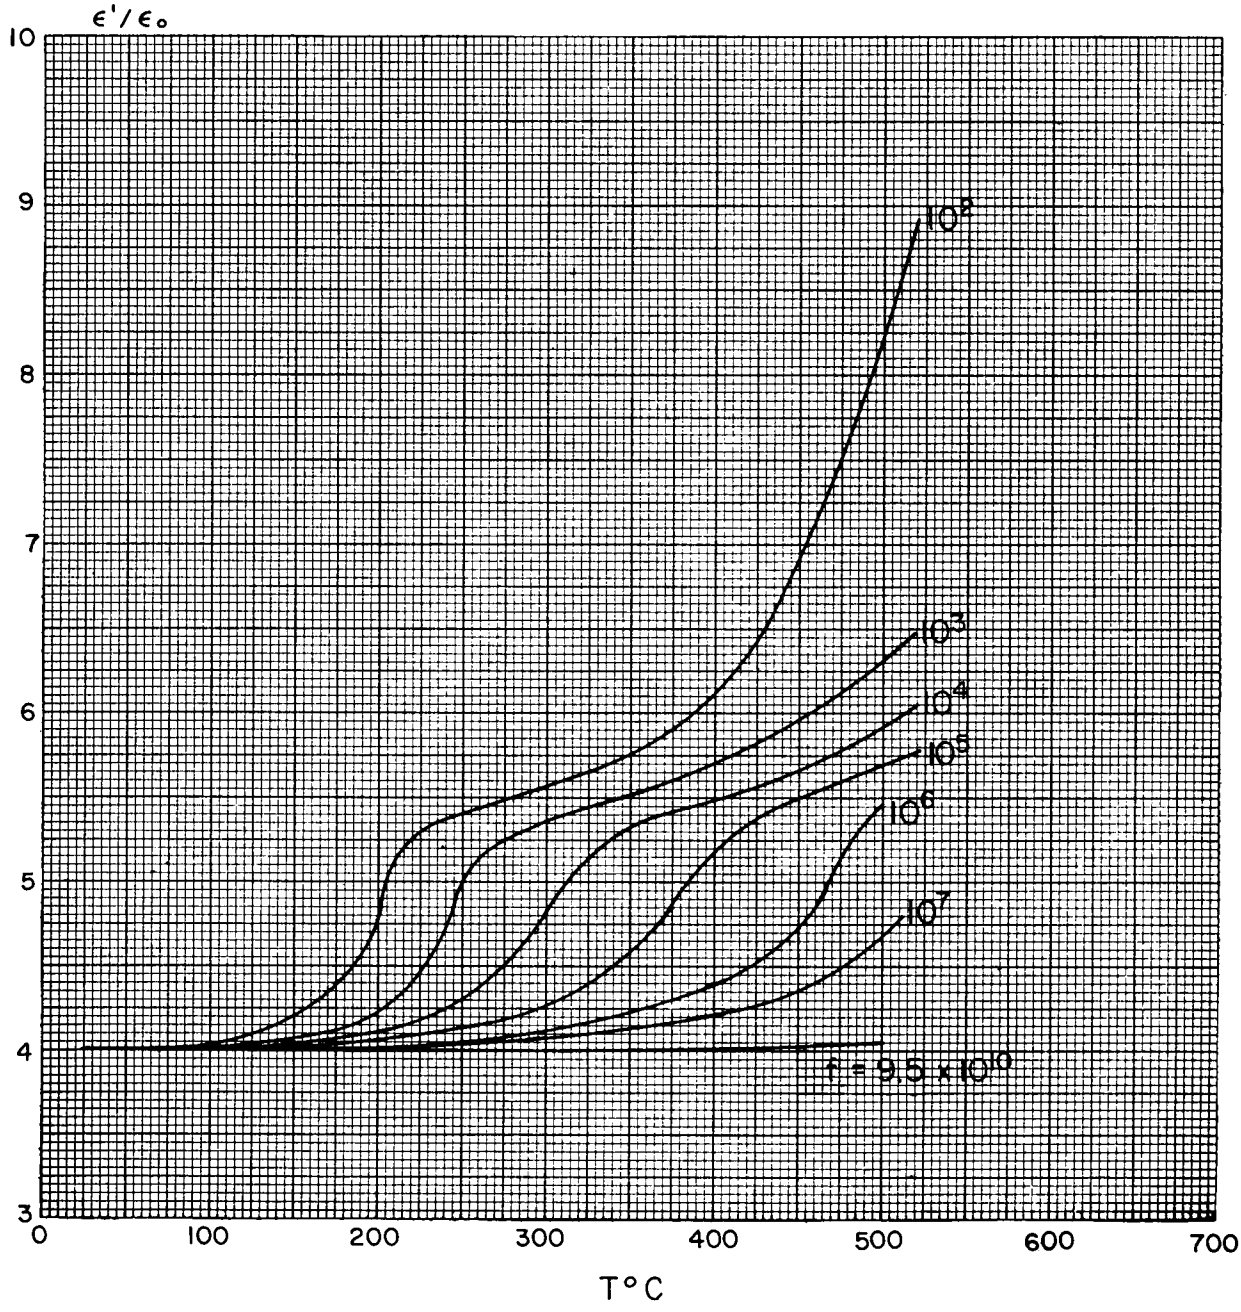

III A 3. Glasses


Corning glass 7070 Corning

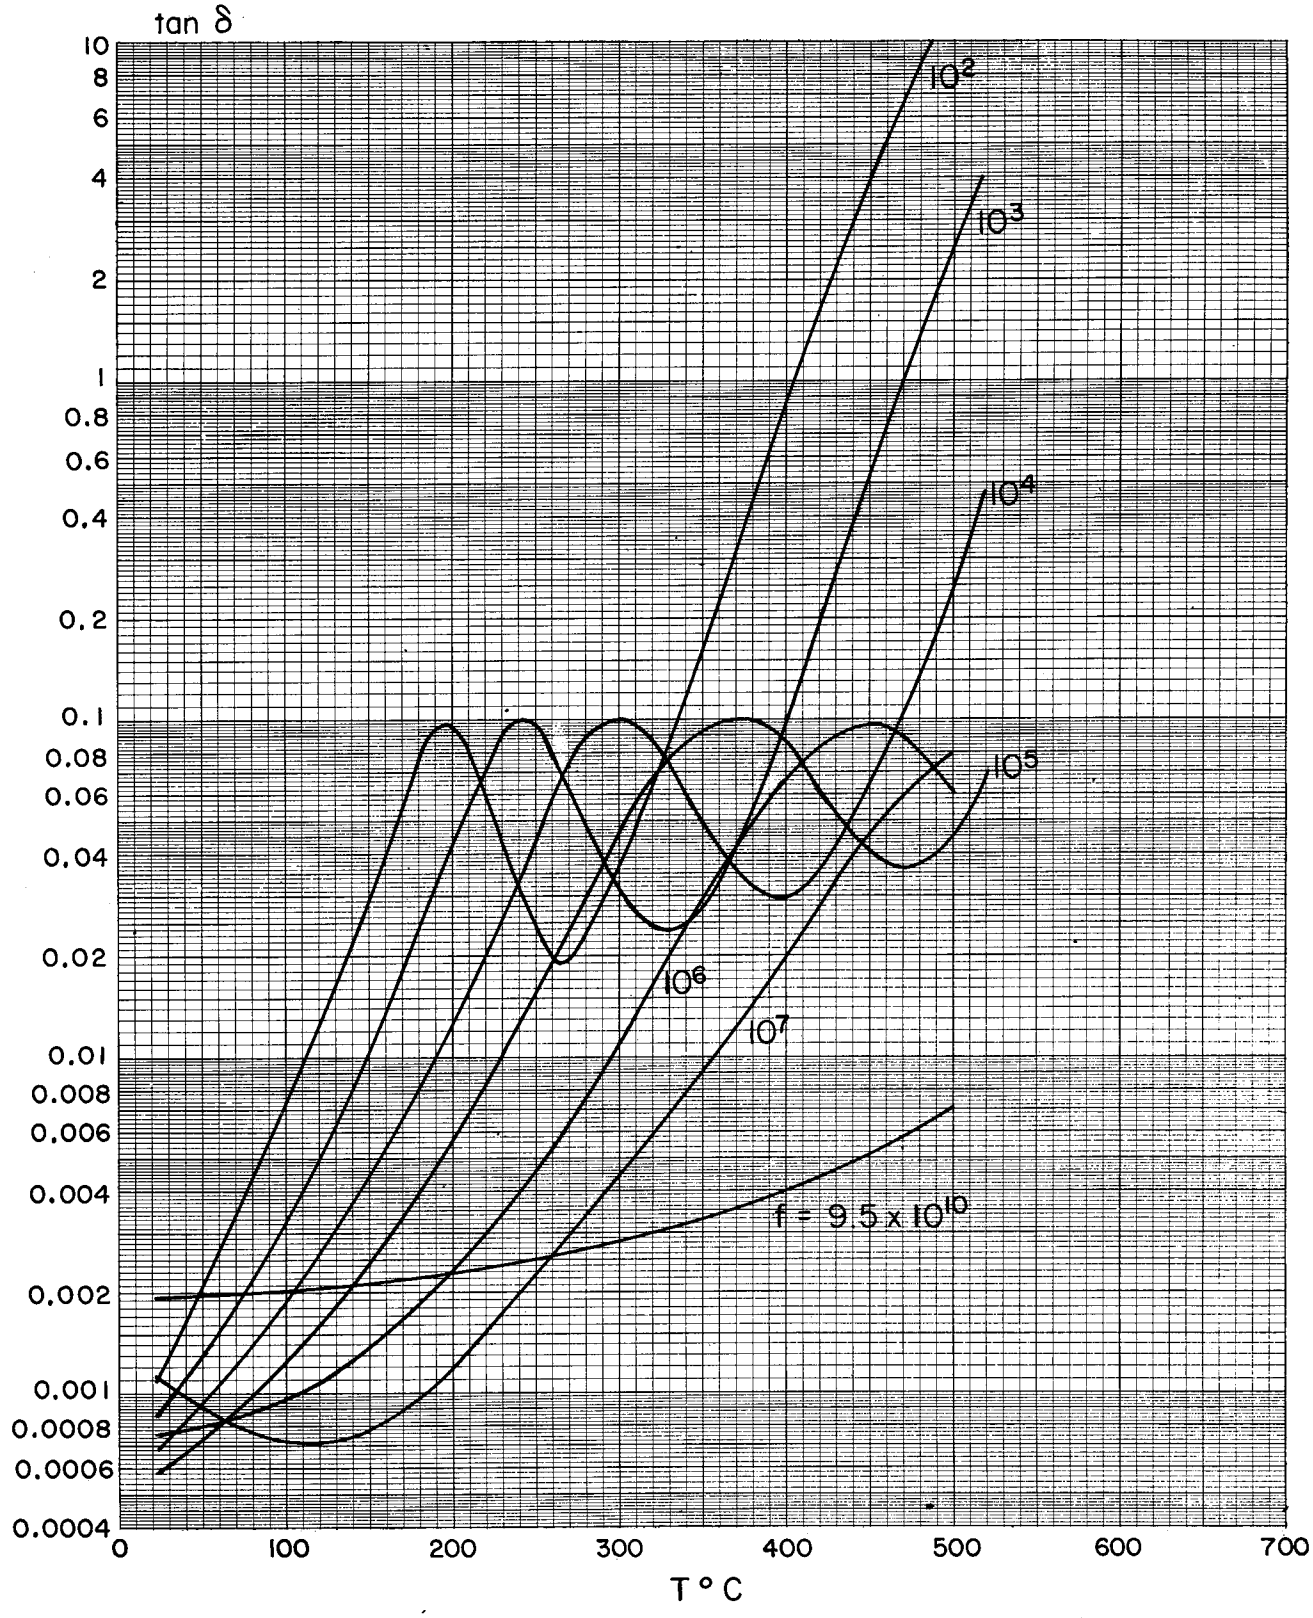

III A 3. Glasses


Corning 7900 glass (received 1942, measured 1957)

Corning

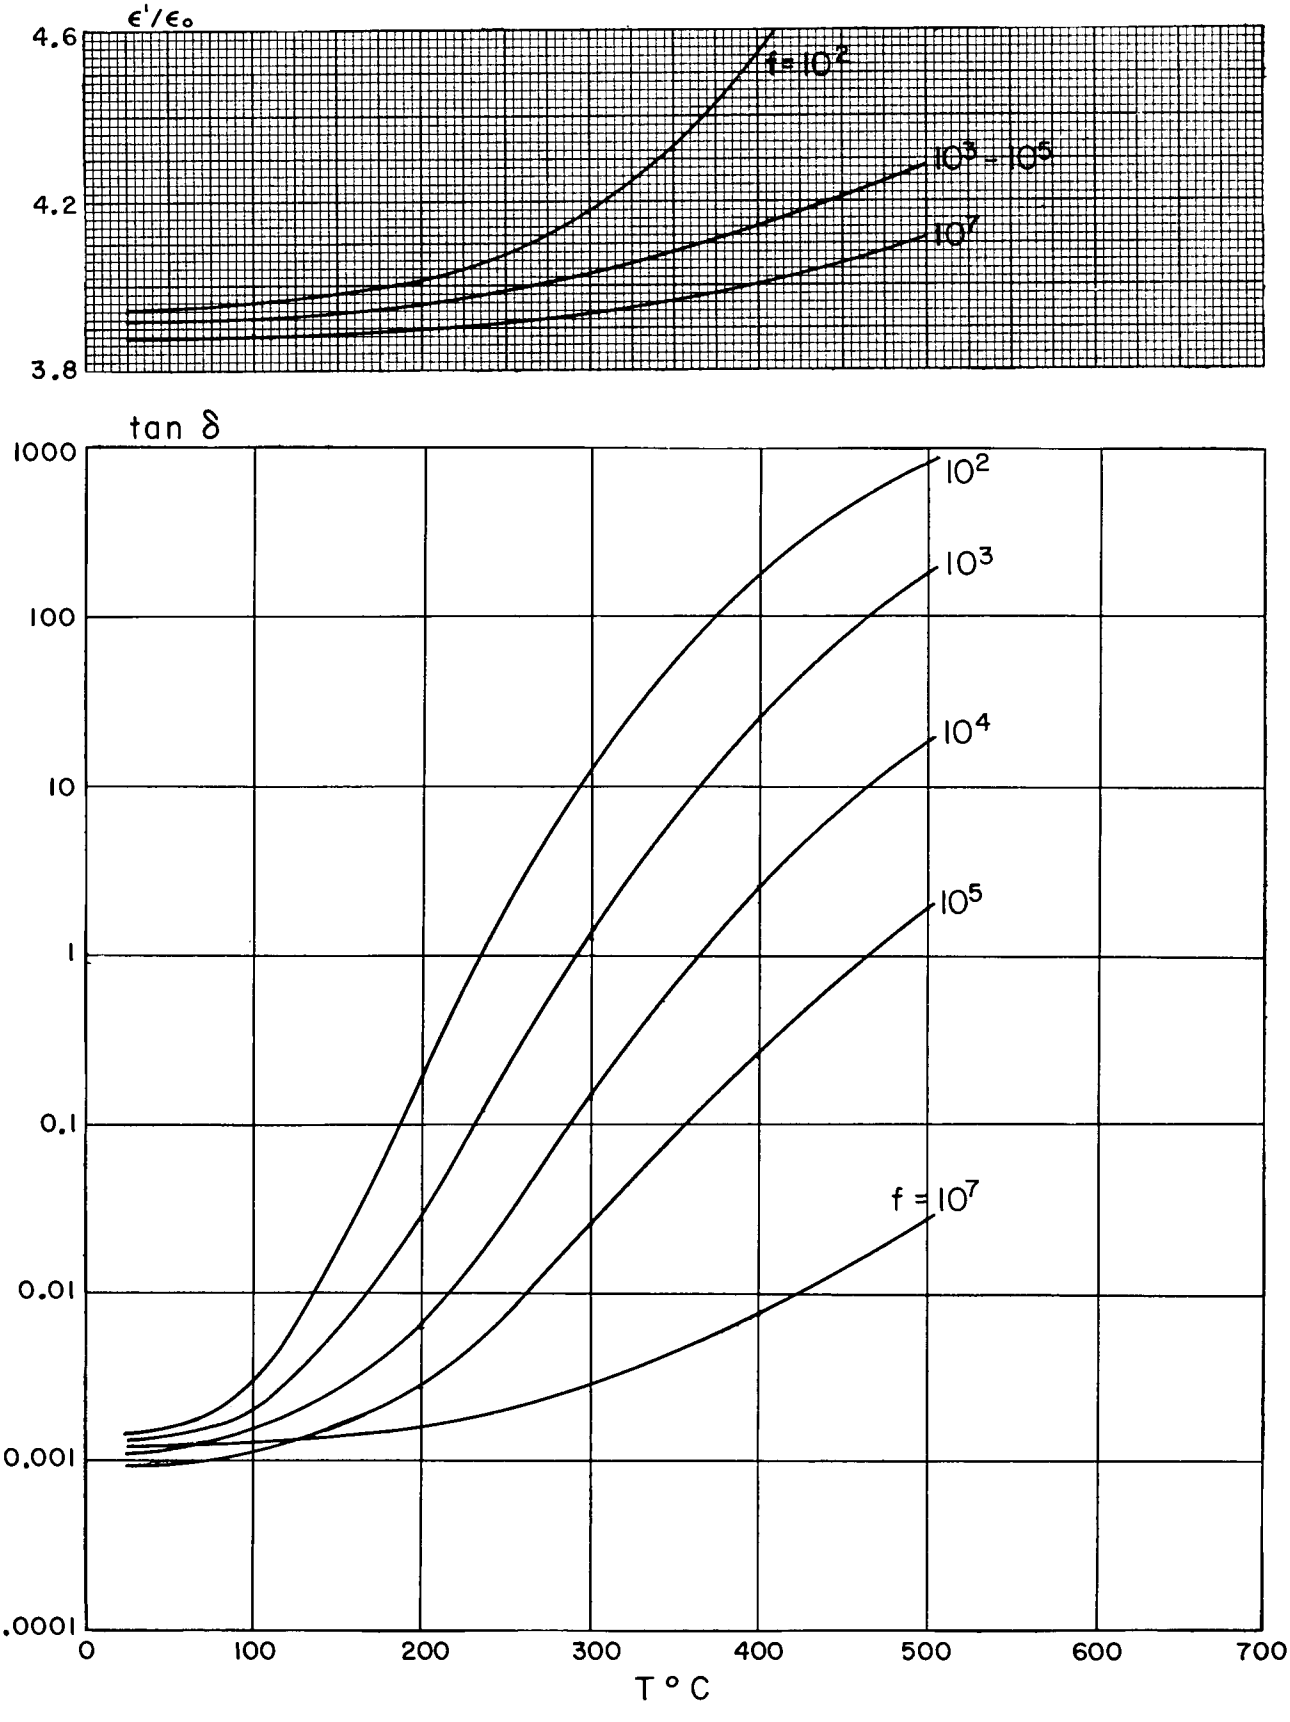


III A 3. Glasses

"Ceram" 61-1 Corning Glass

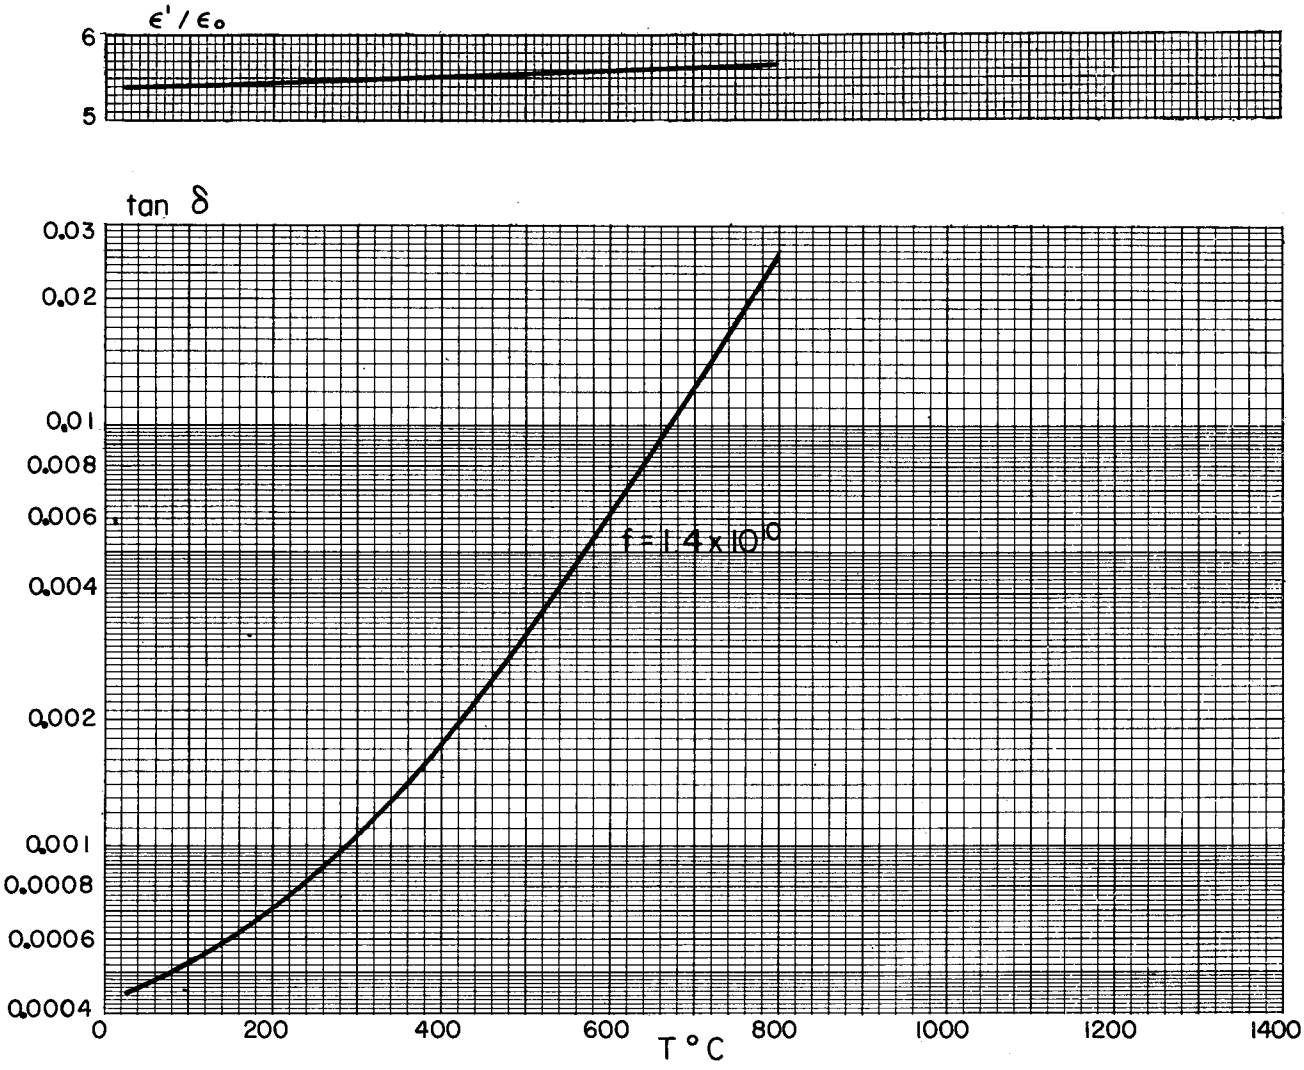


III A 3. Glasses

"Ceram" 61-2 Corning Glass

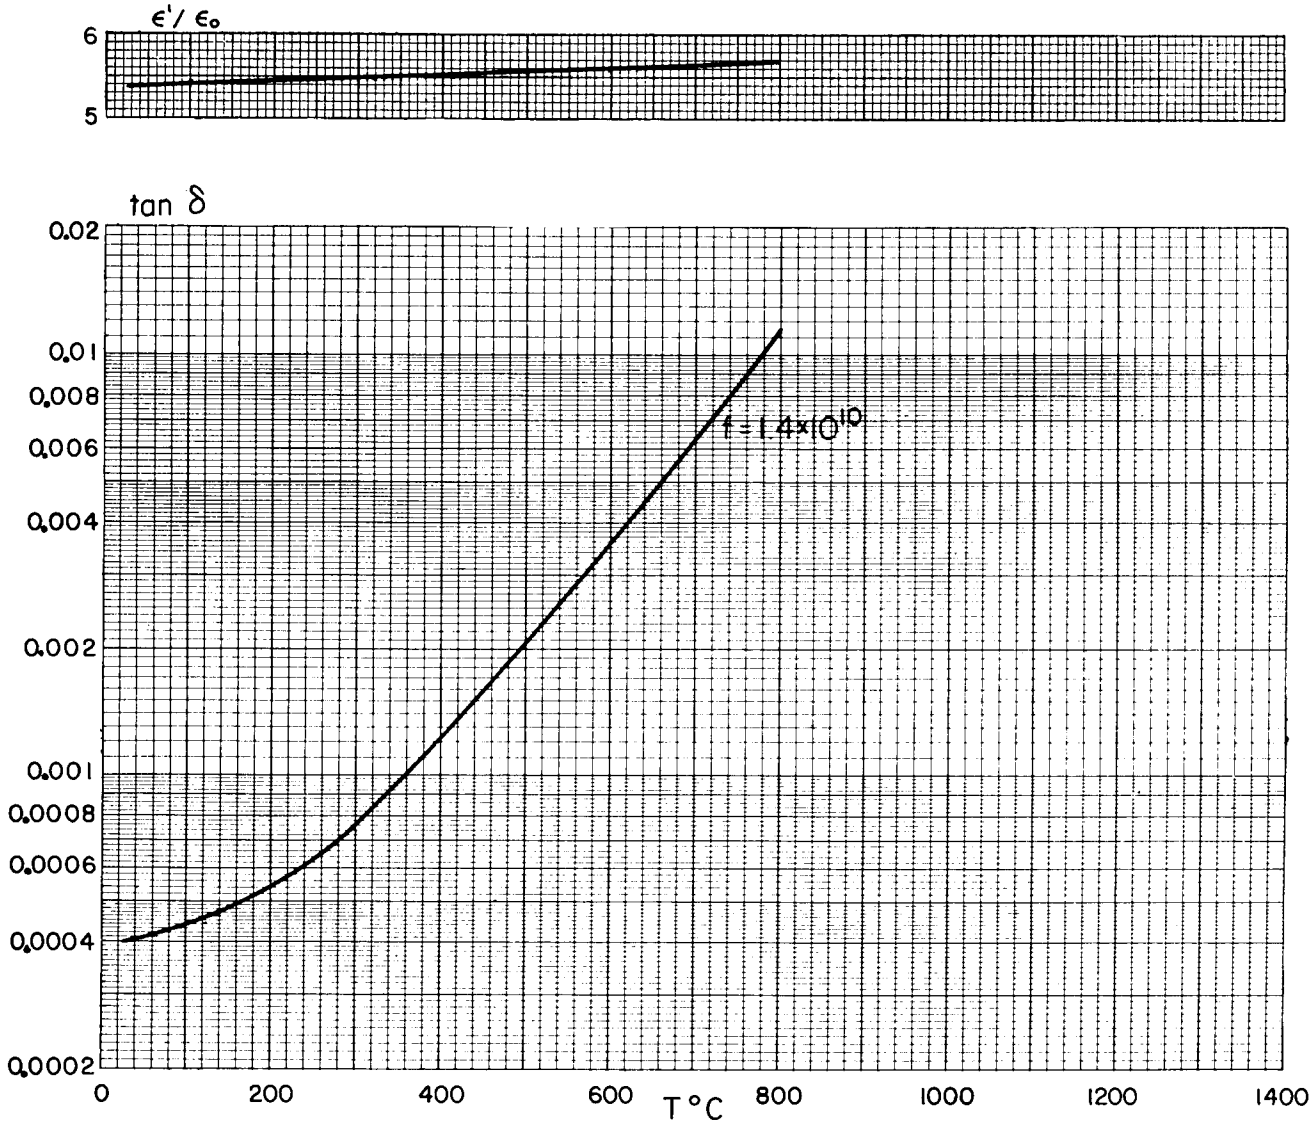

III A 3. Glasses


'Ceram' 61-3 Corning Glass

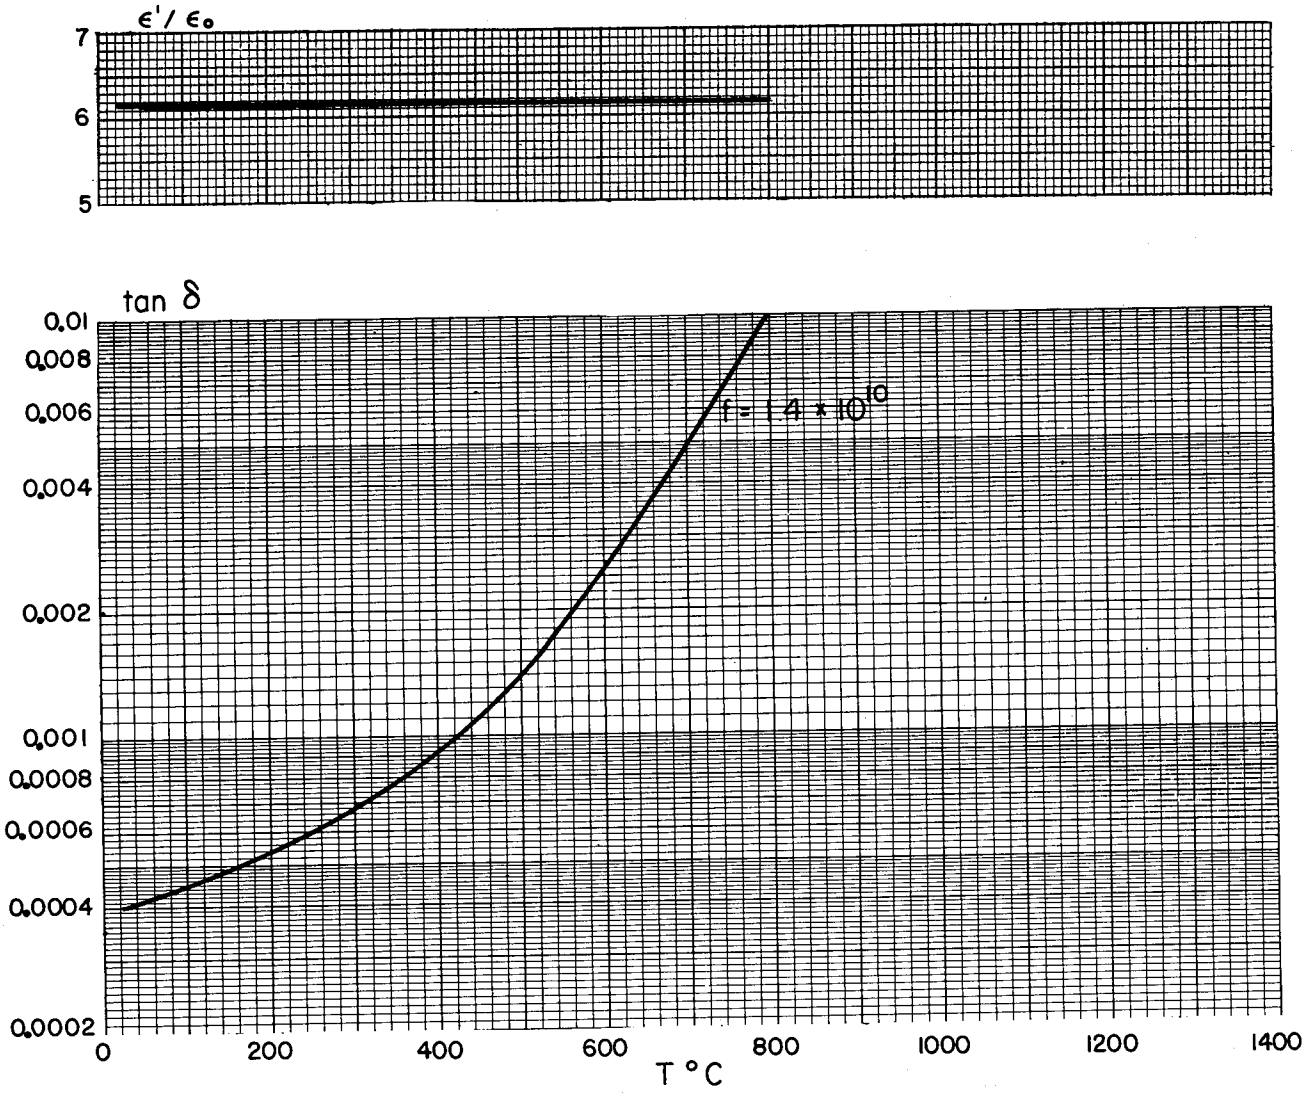

III A 3. Glasses


"Ceram" 61-4

Corning Glass

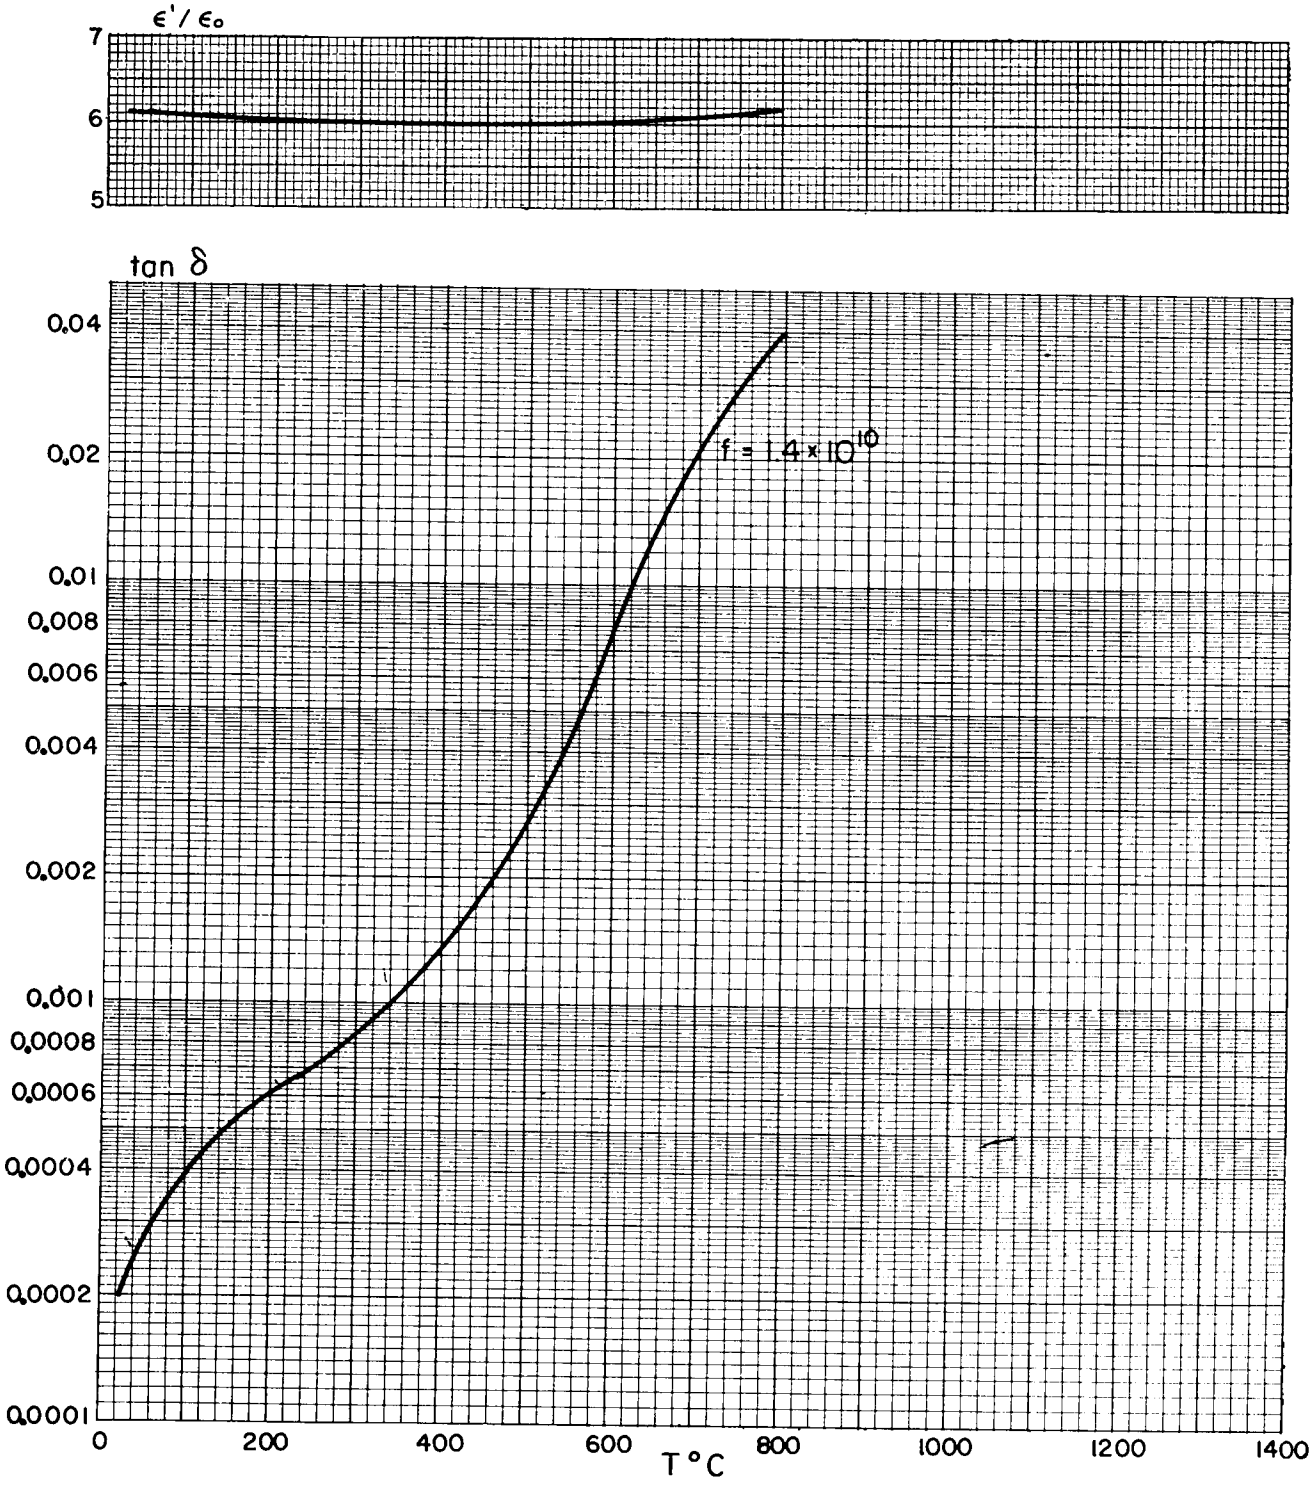

III A 3. Glasses


"Ceram" 61-5 — Corning Glass

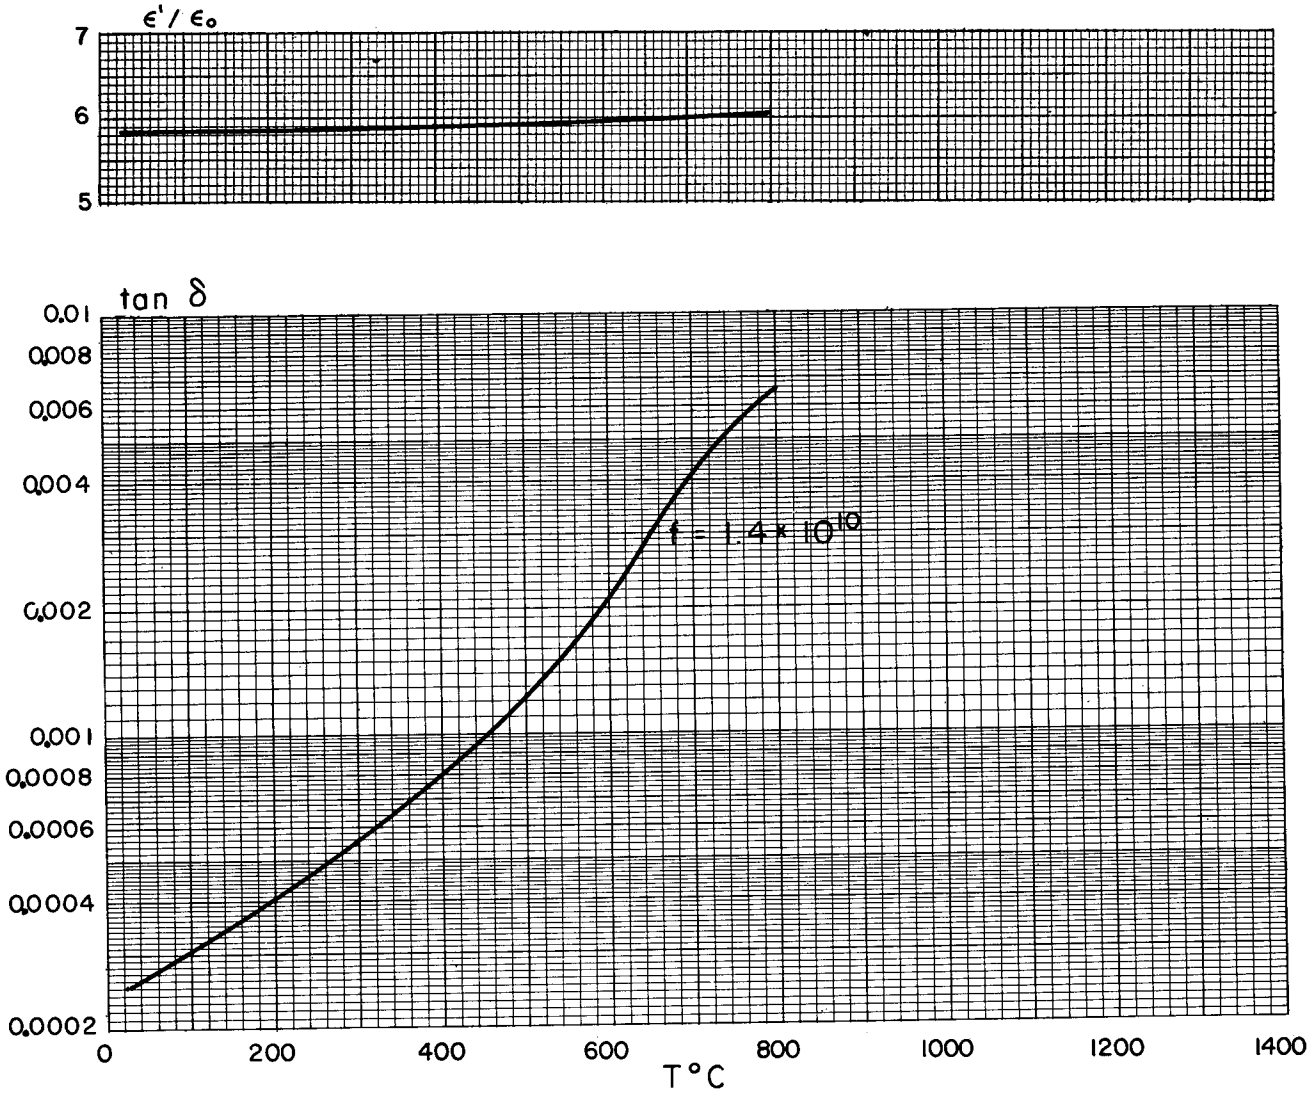

III A 3. Glasses

Fused Silica 915 c


Corning

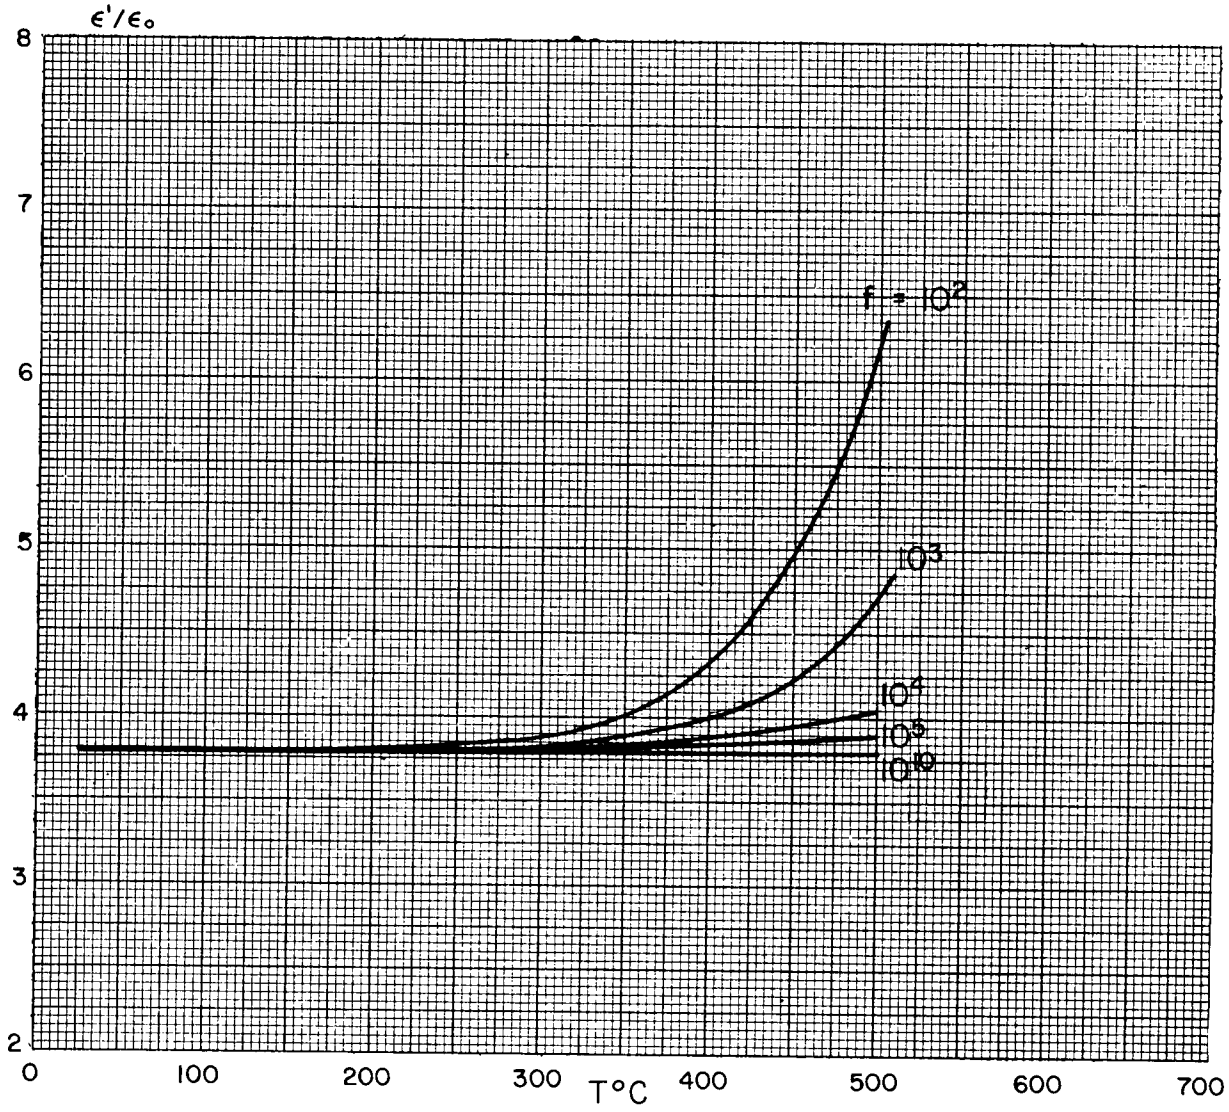

III A 3. Glasses

Fused Silica 915 c


Corning

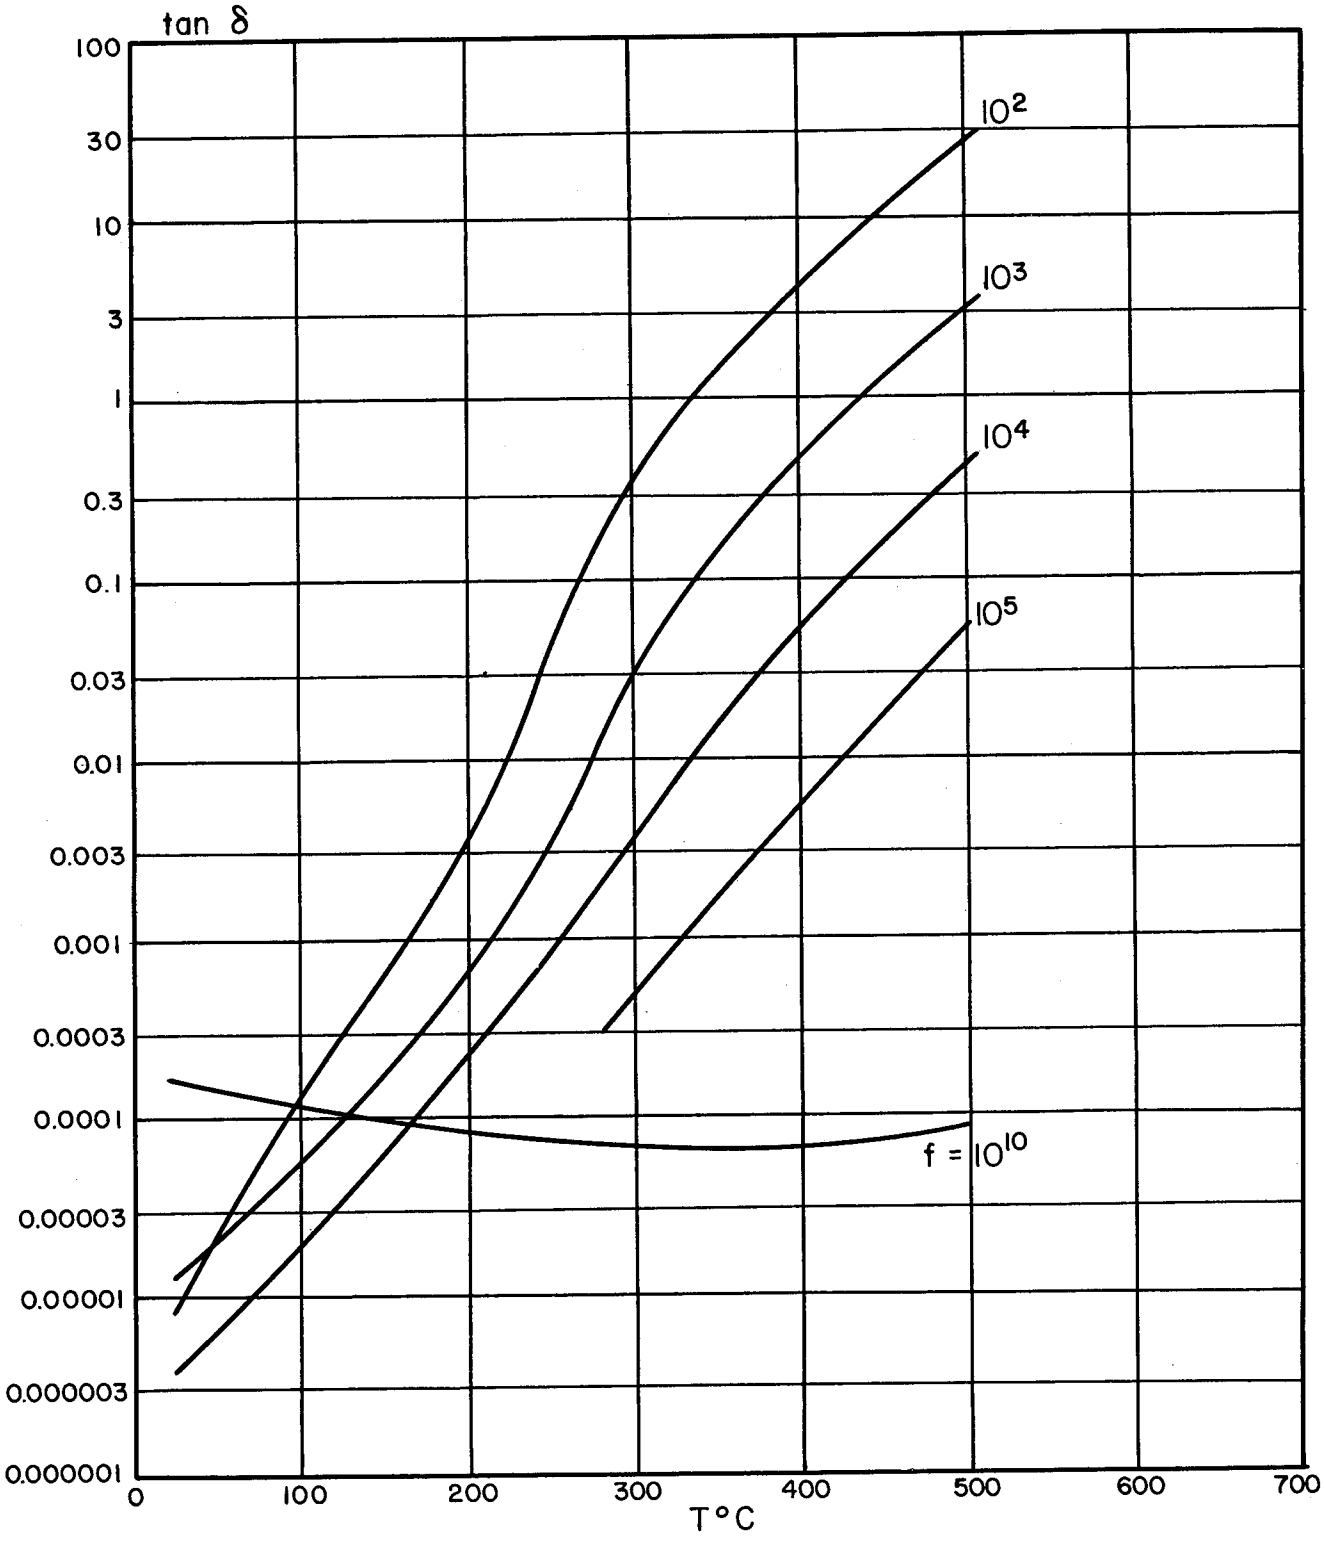

III A 3. Glasses

Fused Quartz

General Electric, Cleveland

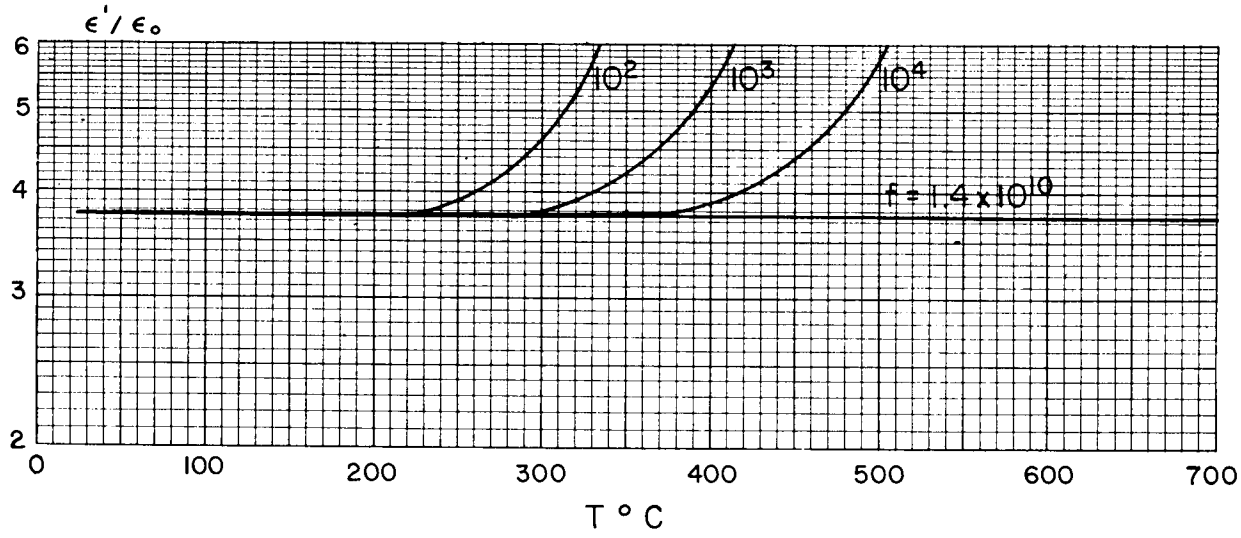


At 800°C, 1.4×10^{10} cycles, $\epsilon'/\epsilon_o = 3.76$ and $\tan \delta = 0.00048$.

At 1200°C, 5×10^{10} cycles, $\epsilon'/\epsilon_o = 3.8\text{-}3.9$ and $\tan \delta < 0.002$.

III A 3. Glasses


Fused Quartz

General Electric, Cleveland

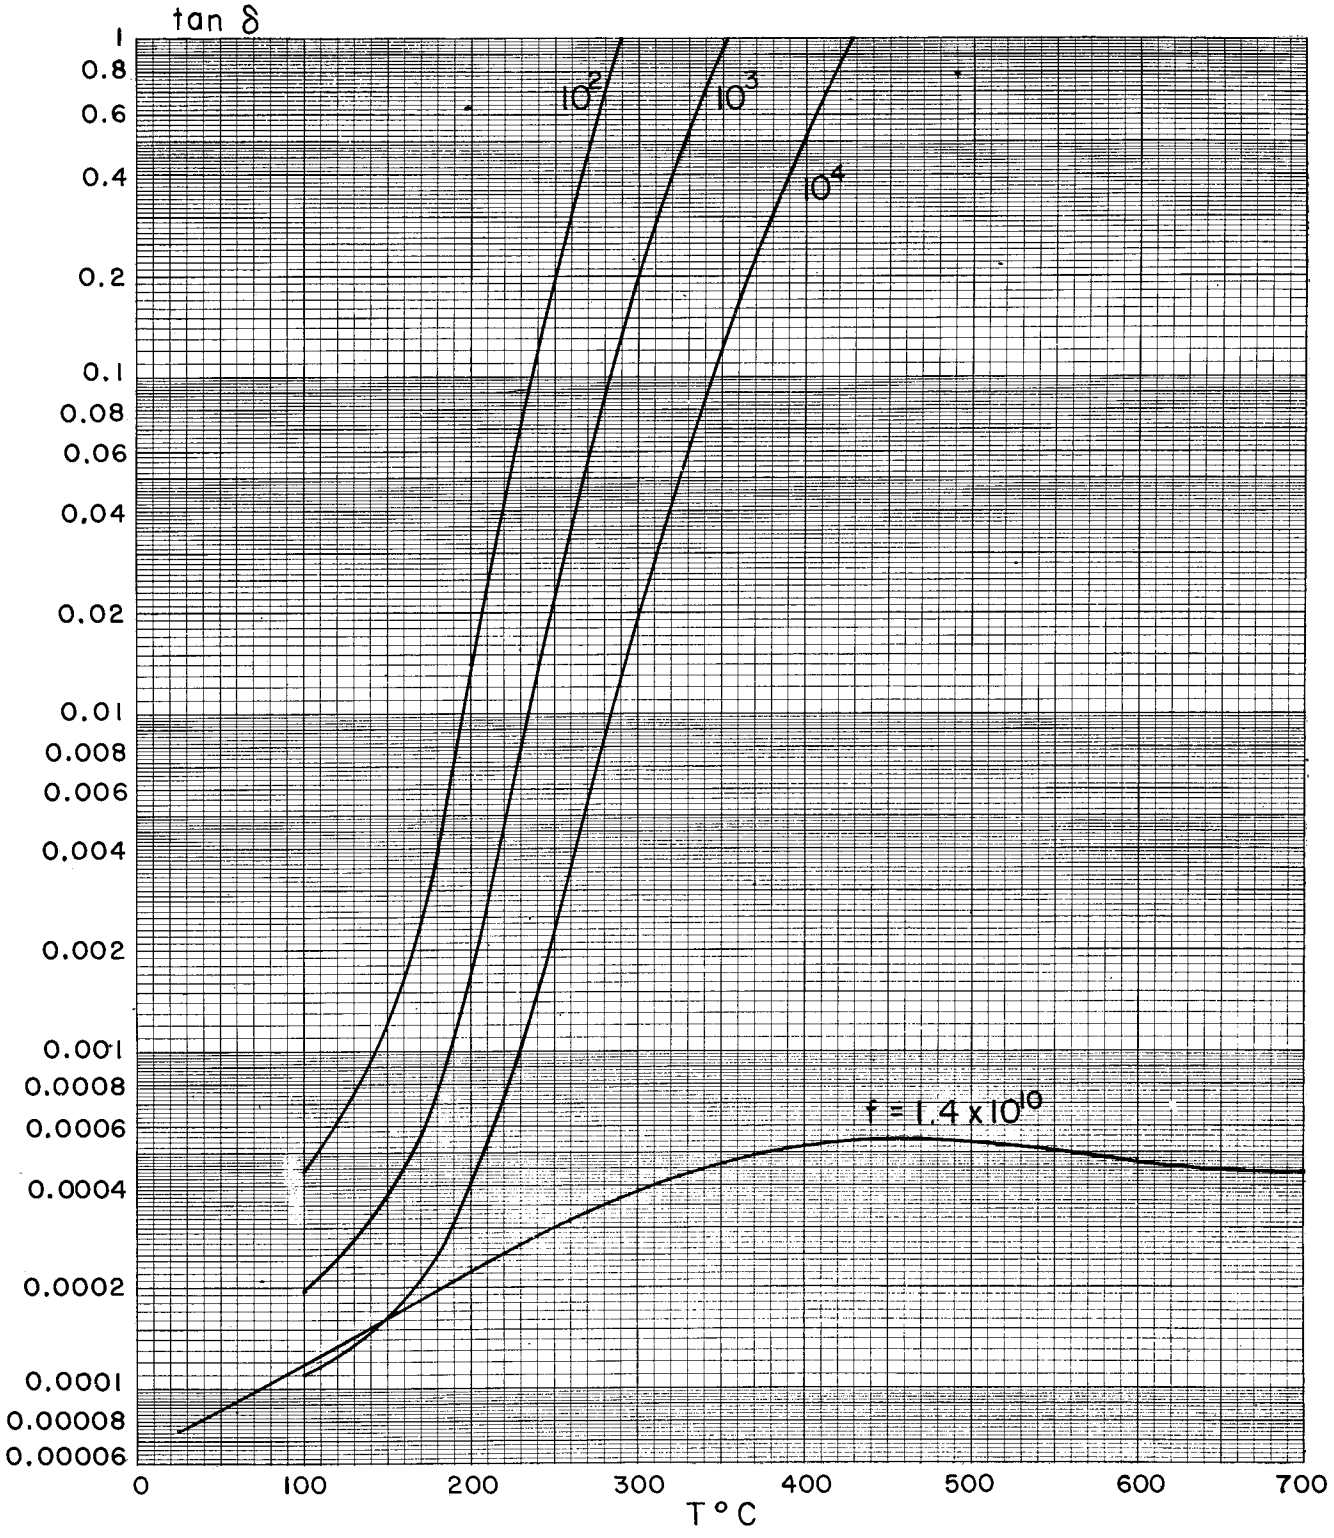


III A 4. Miscellaneous Inorganics

"Amplifilm" Aircraft Marine

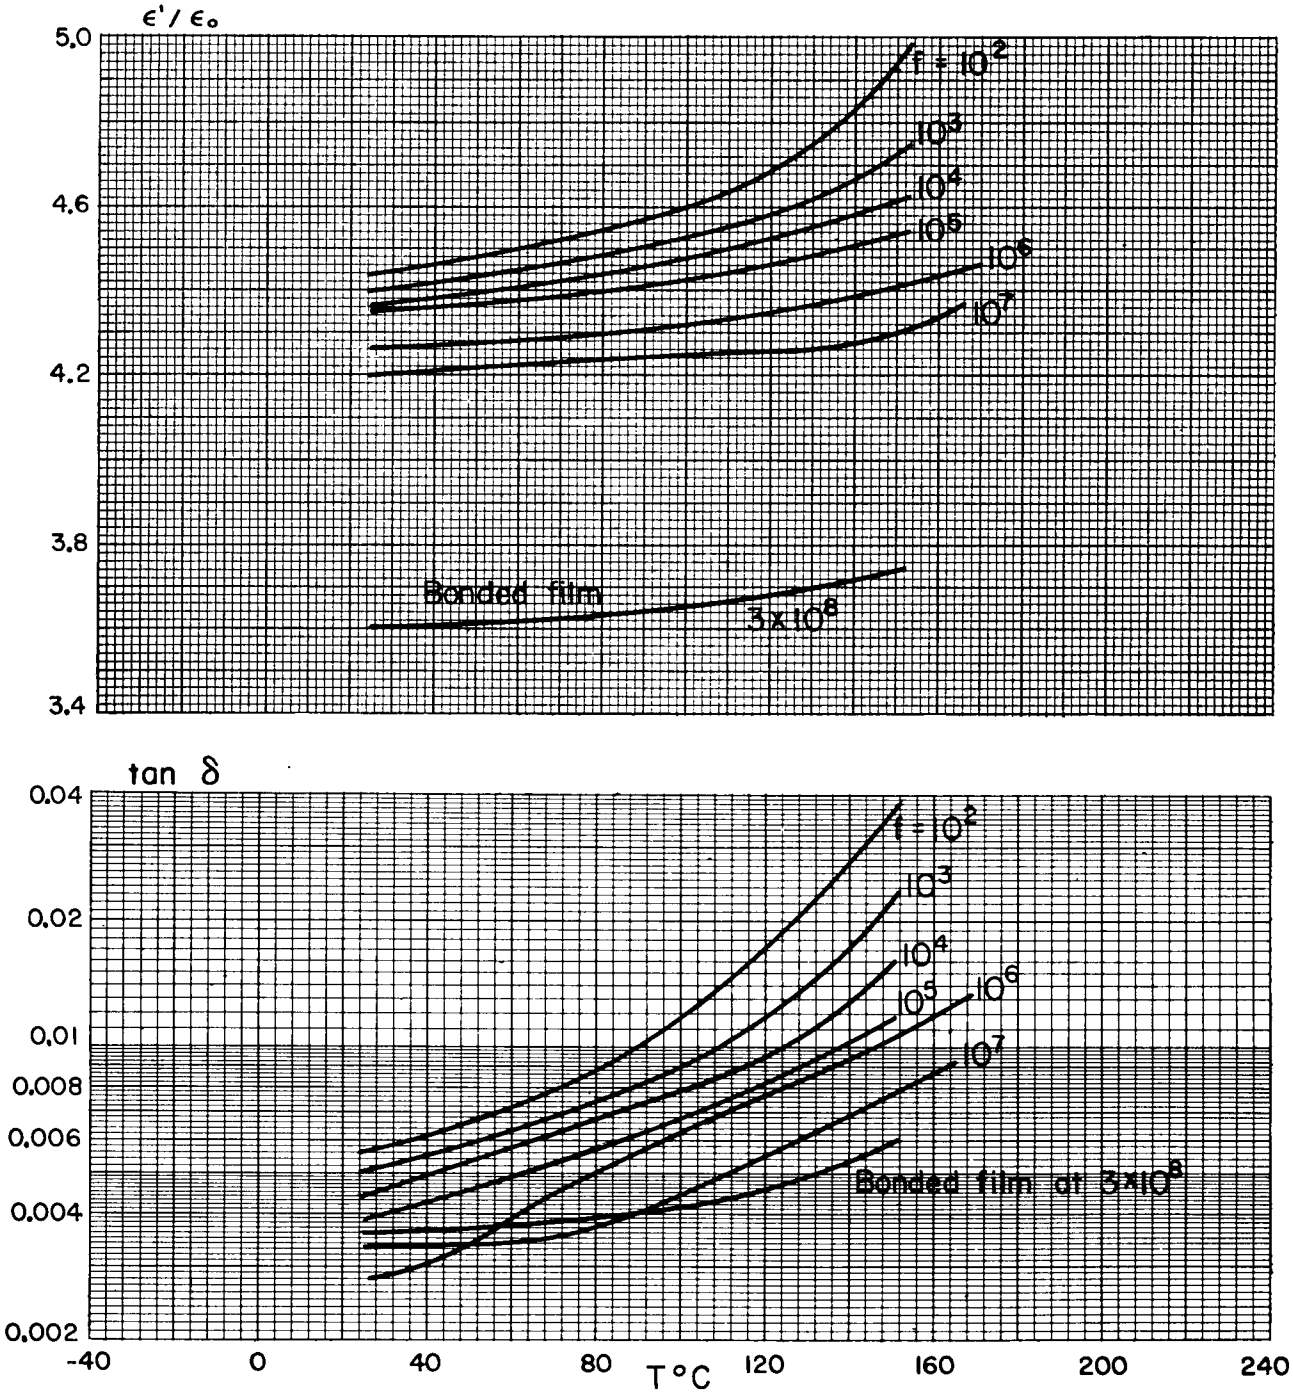


III A 4. Miscellaneous Inorganics

"AlSiMag" 602 American Lava

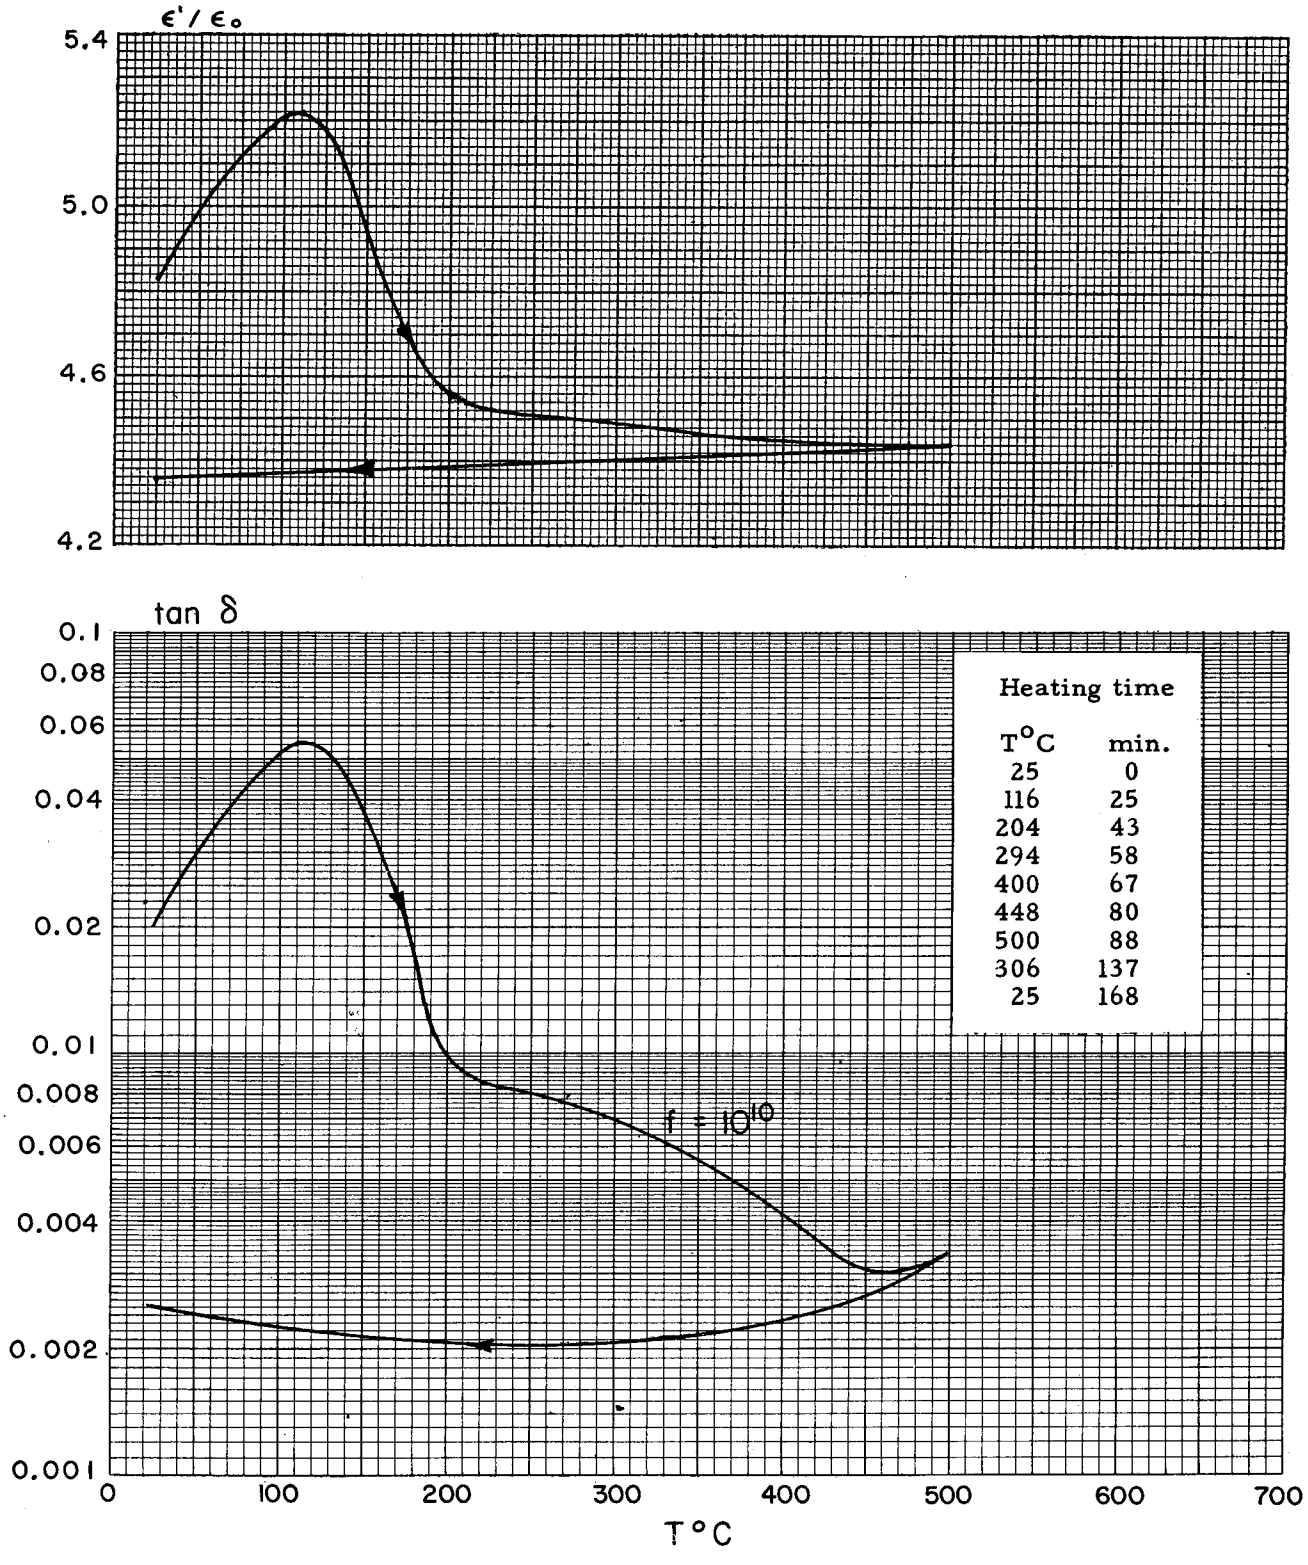


III A 4. Miscellaneous Inorganics

Hot Pressed Boron Nitride — Carborundum Co.

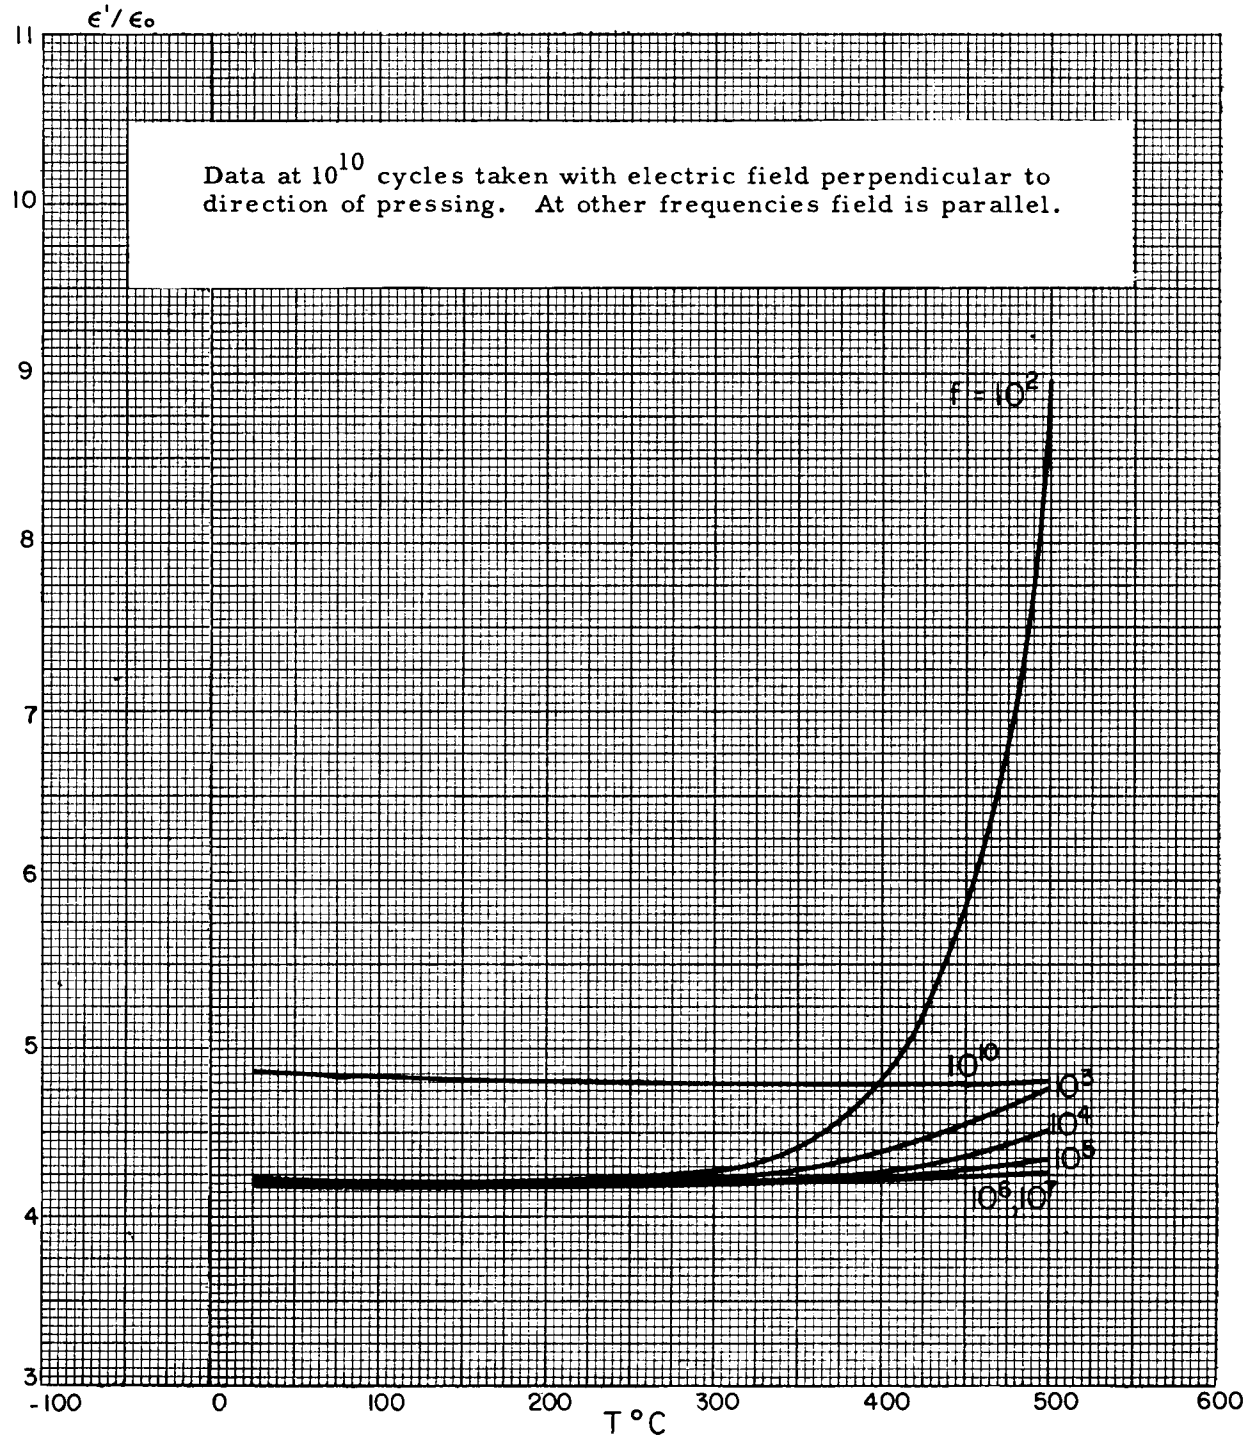


III A 4. Miscellaneous Inorganics

Hot Pressed Boron Nitride — Carborundum Co.

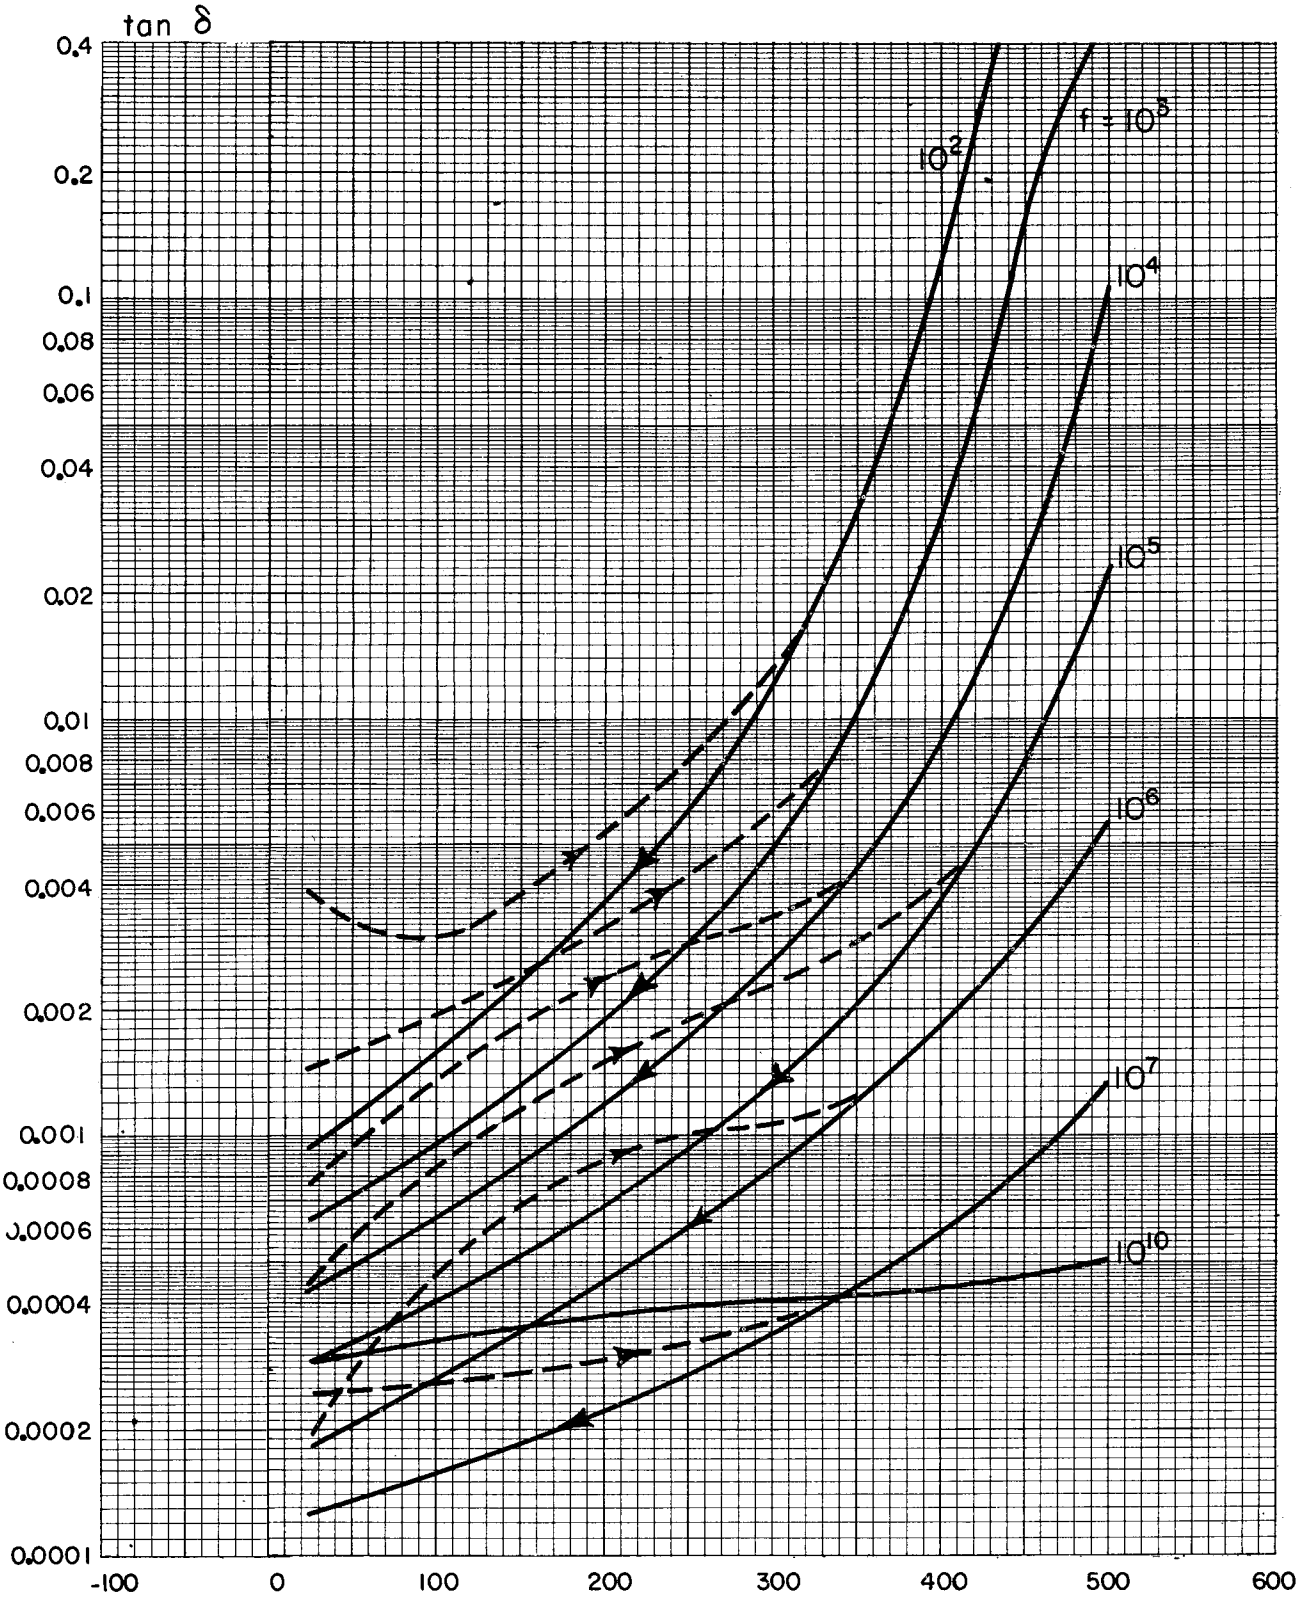


III A 4. Miscellaneous Inorganics

"Fiberfrax" Board (density 0.50 gm/cc) Carborundum

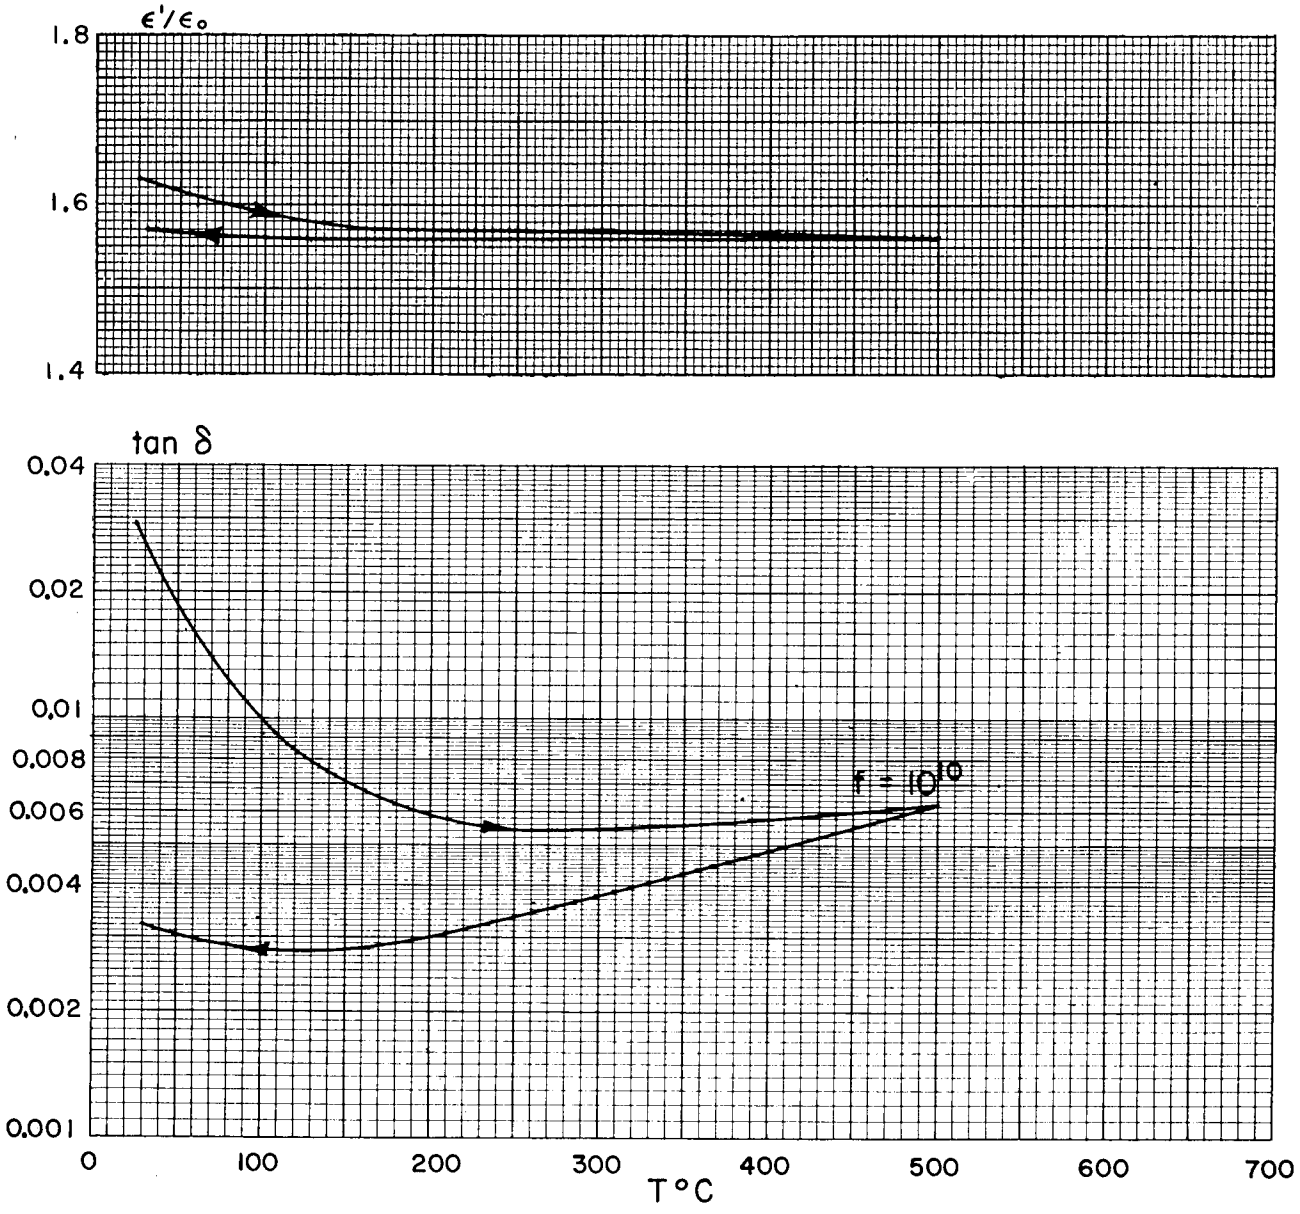


III A 4. Miscellaneous Inorganics

Silicon nitride (0.75) - Boron nitride (0.25) Carborundum

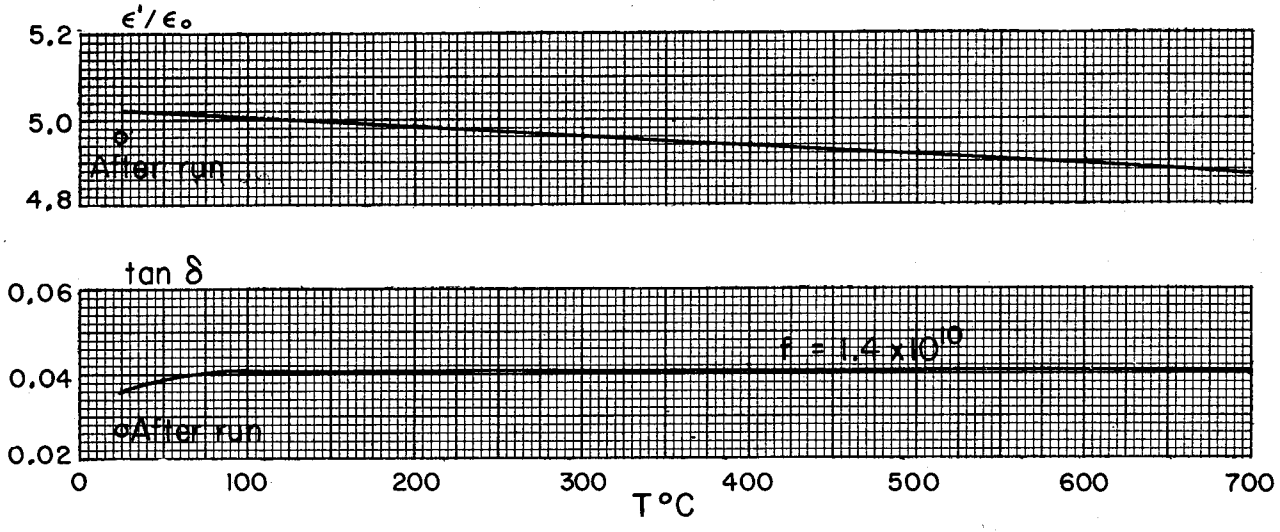


"Supramica" 500 (density 3.04 gm/cc) Mycalex

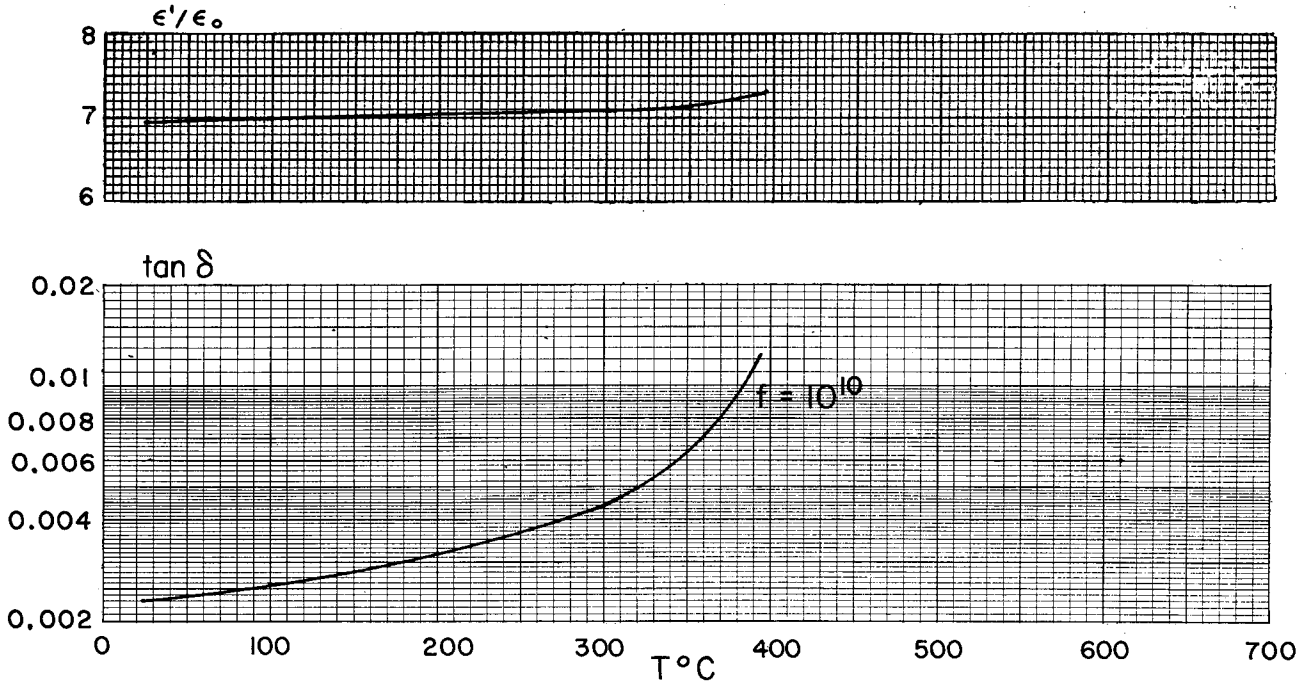


III B 1. Phenolics

"Dilecto" (hot punching) XXX-P-26 Continental Diamond

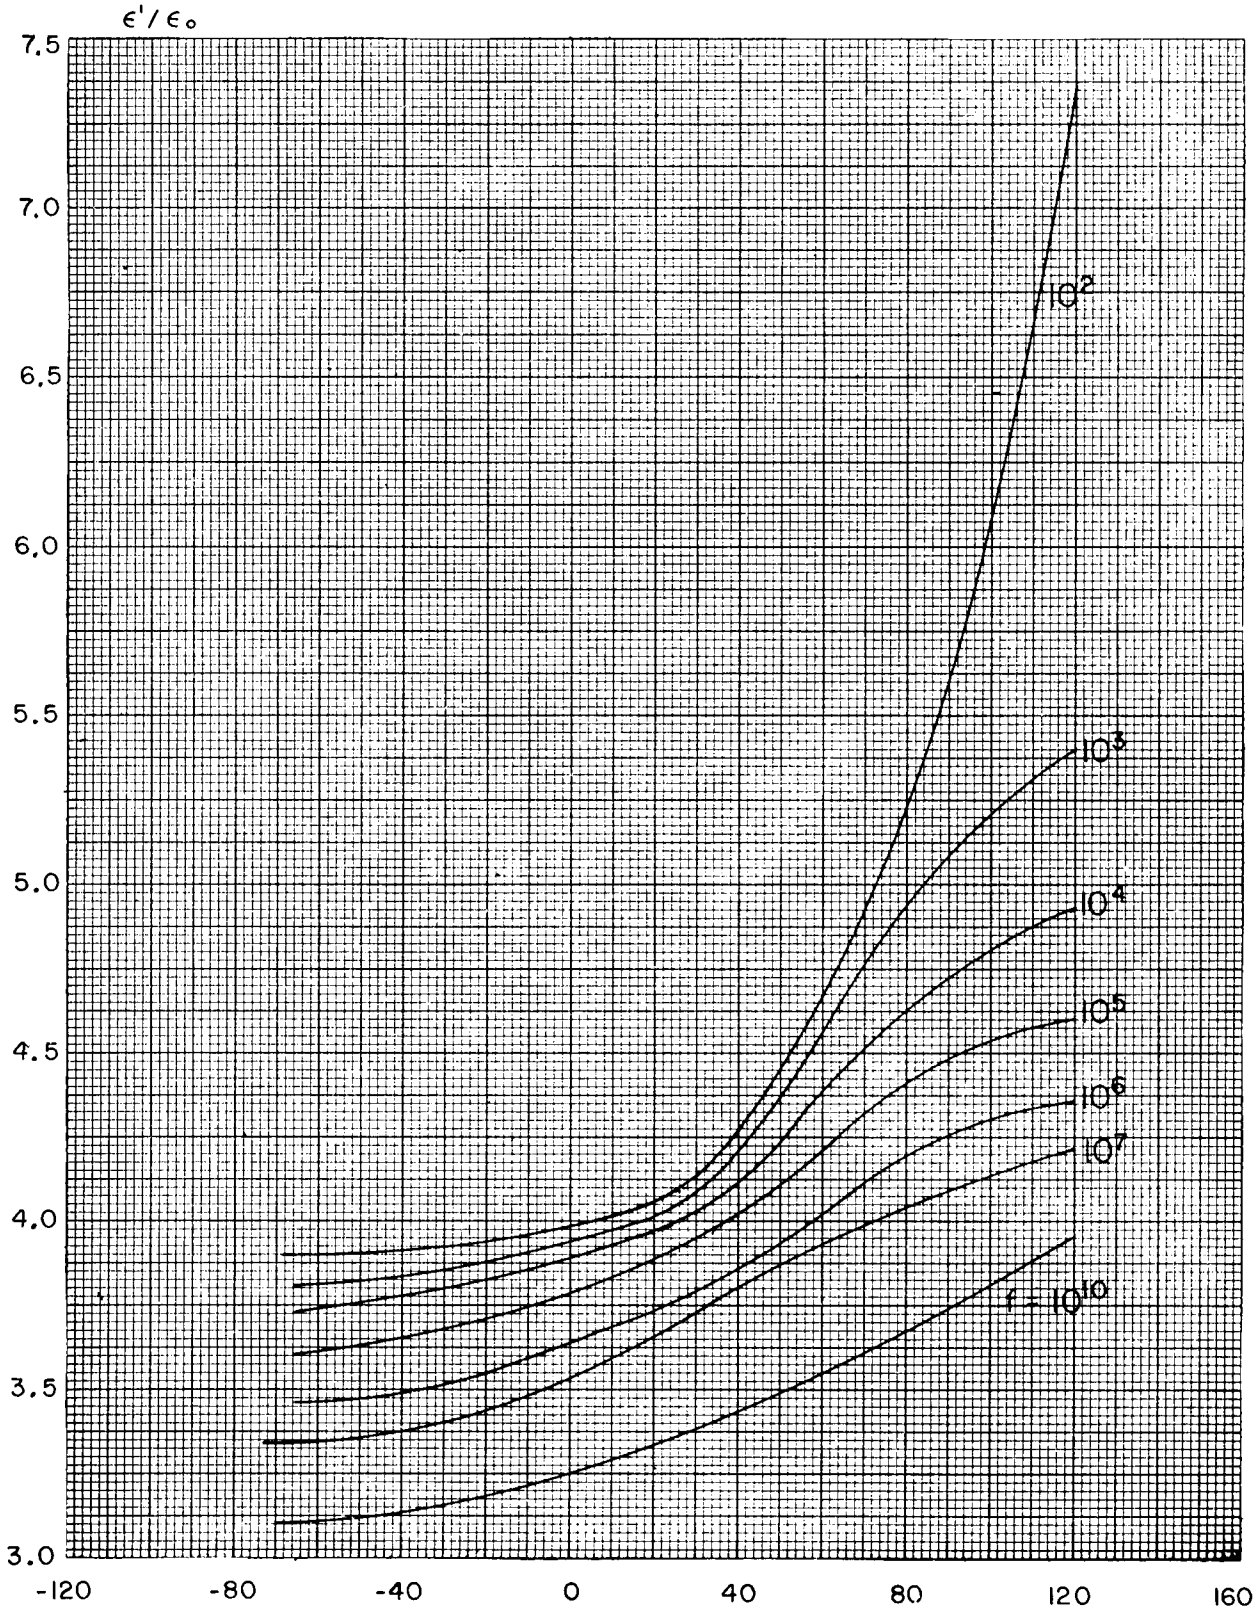


III B 1. Phenolics

"Dilecto" (hot punching) XXX-P-26 Continental Diamond

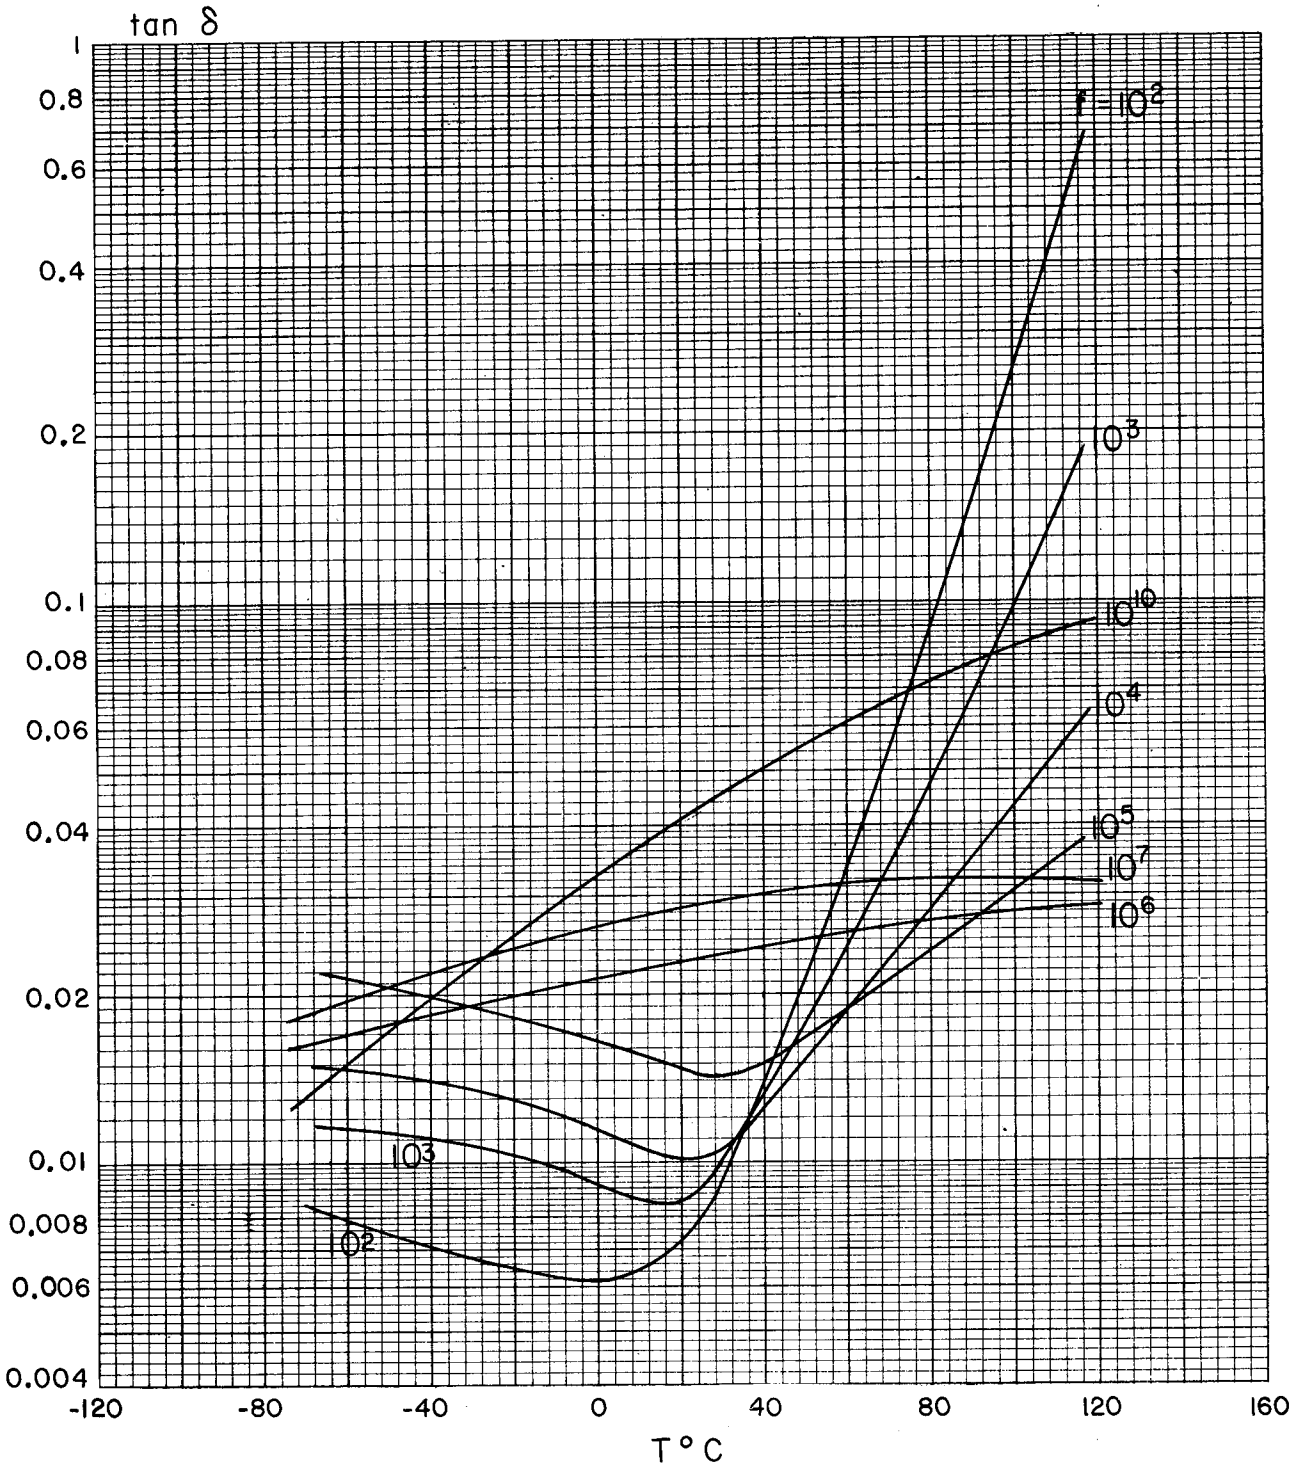


III B 1. Phenolics

"Dilecto" ("Mecoboard") Continental Diamond

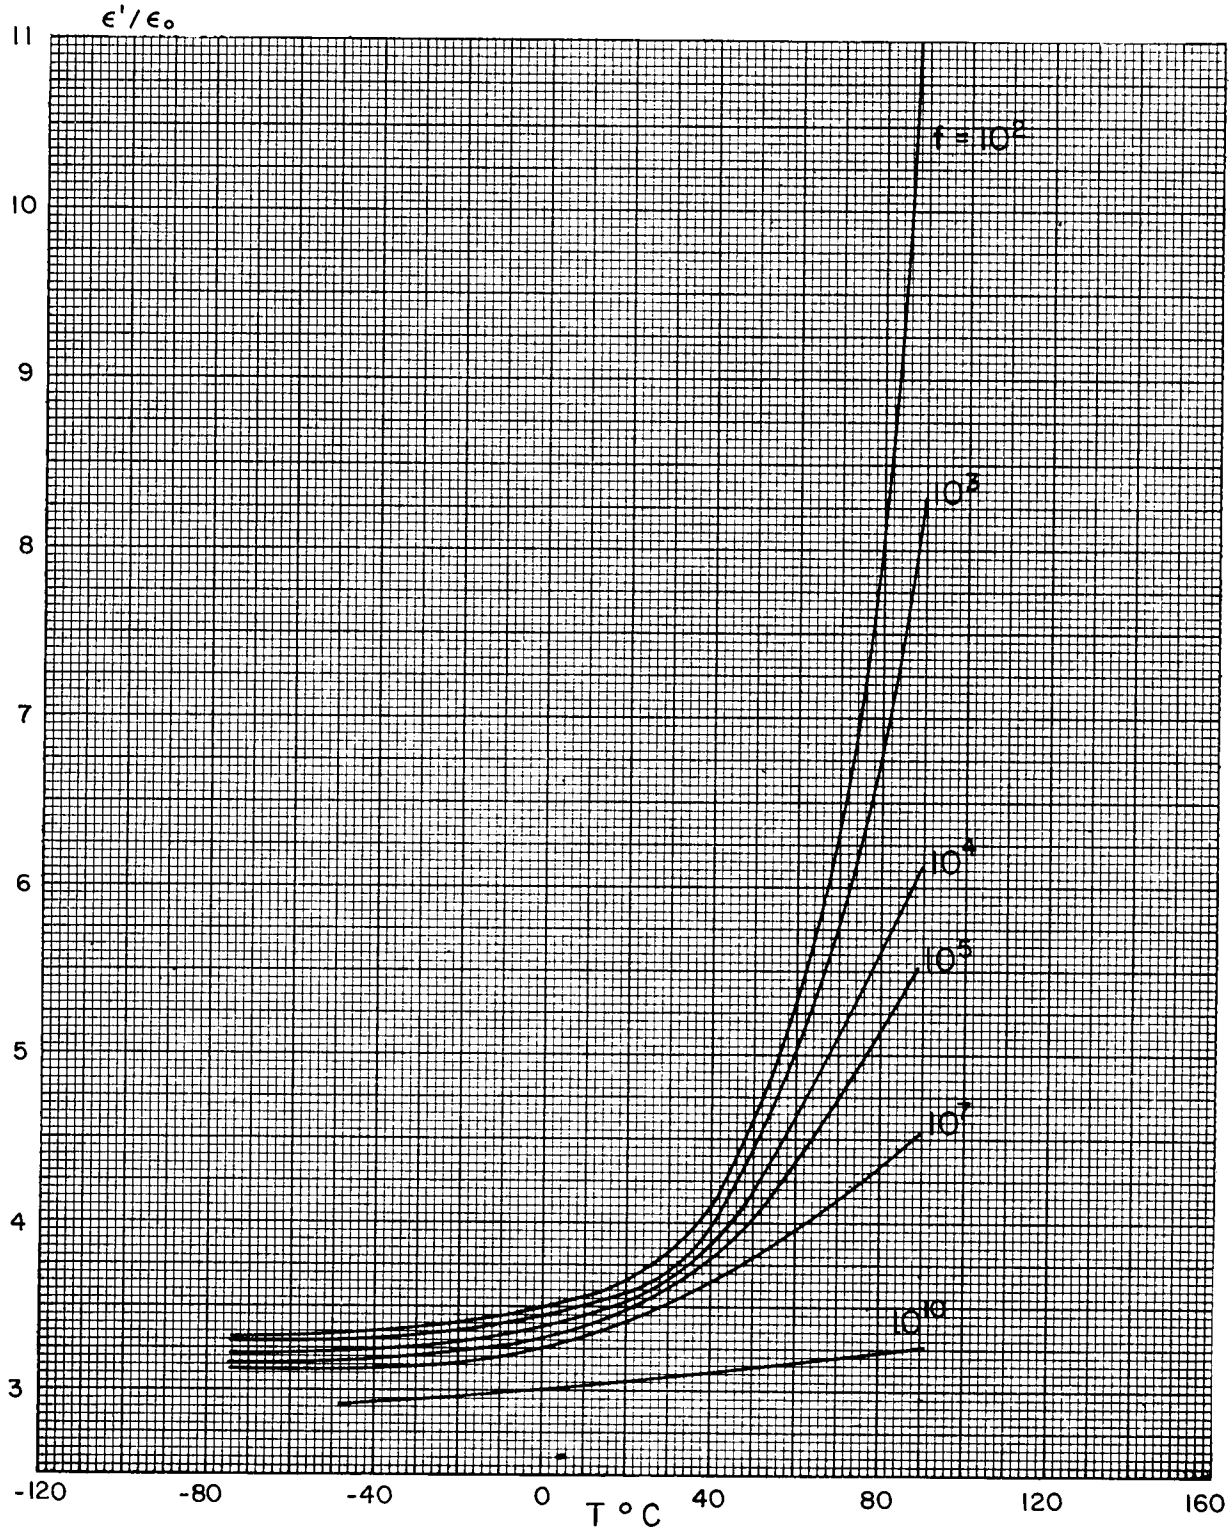


III B 1. Phenolics

"Dilecto" ("Mecoboard") Continental Diamond

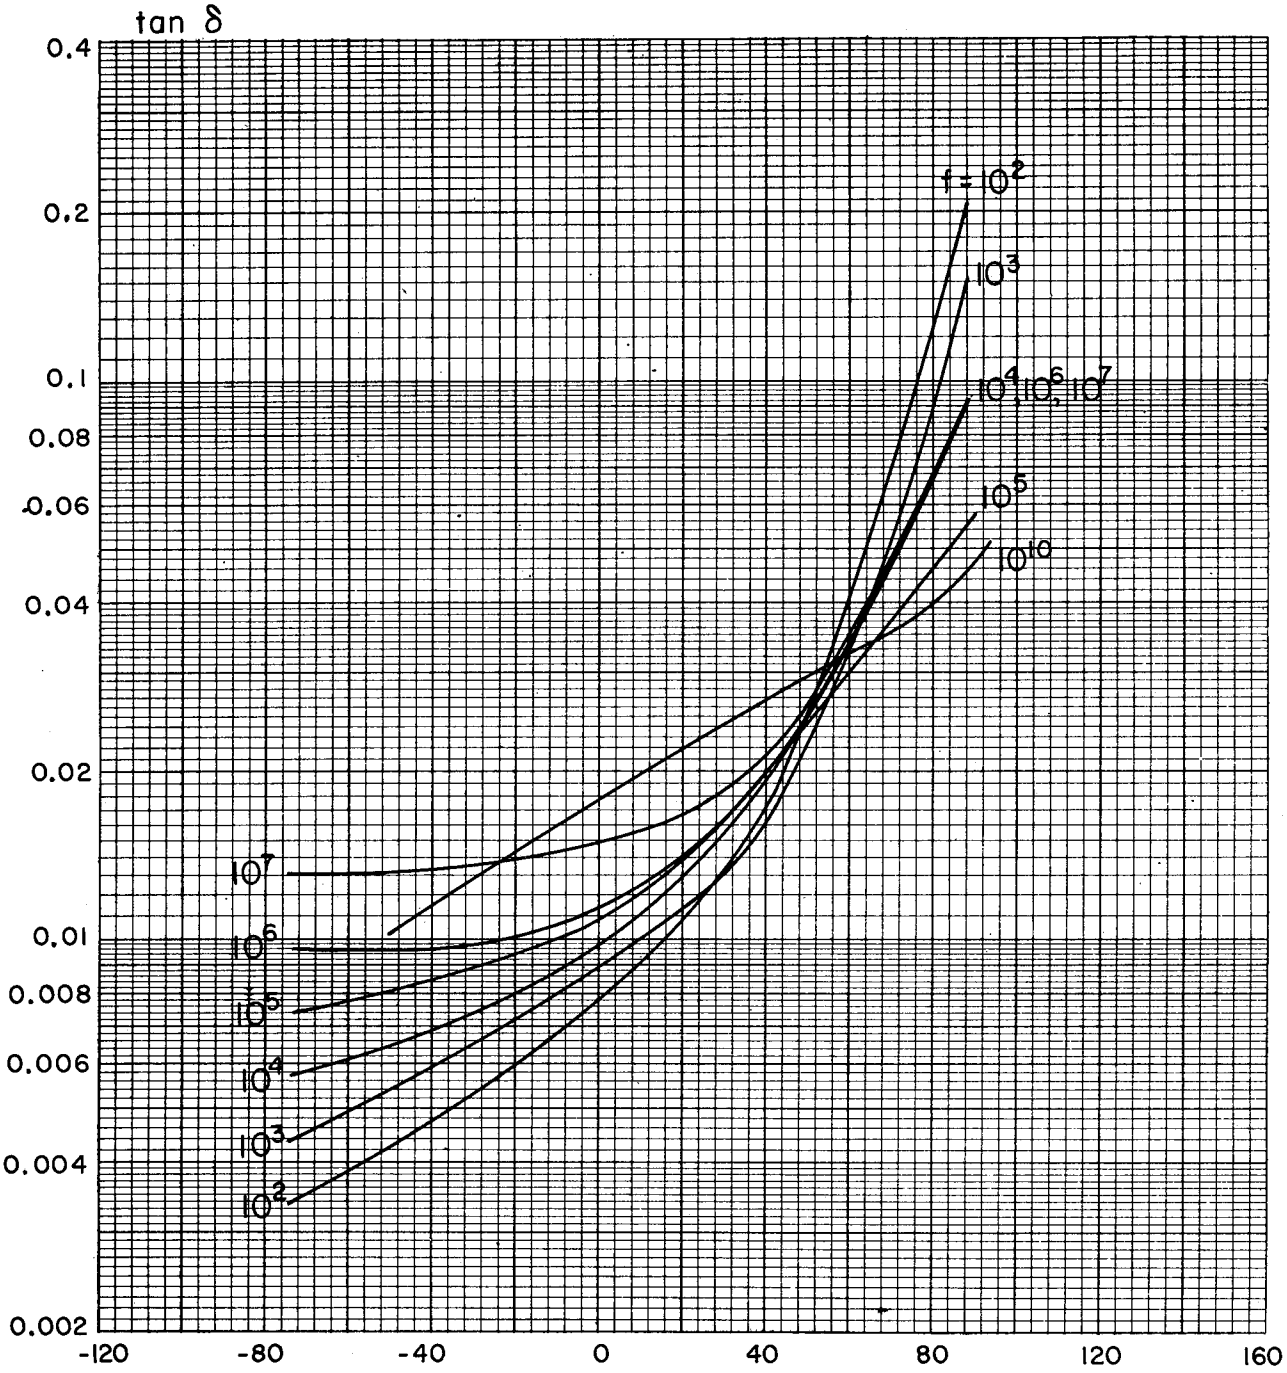

III B 1. Phenolics


Phenolic - asbestos laminate — Goodyear Aircraft Corp.

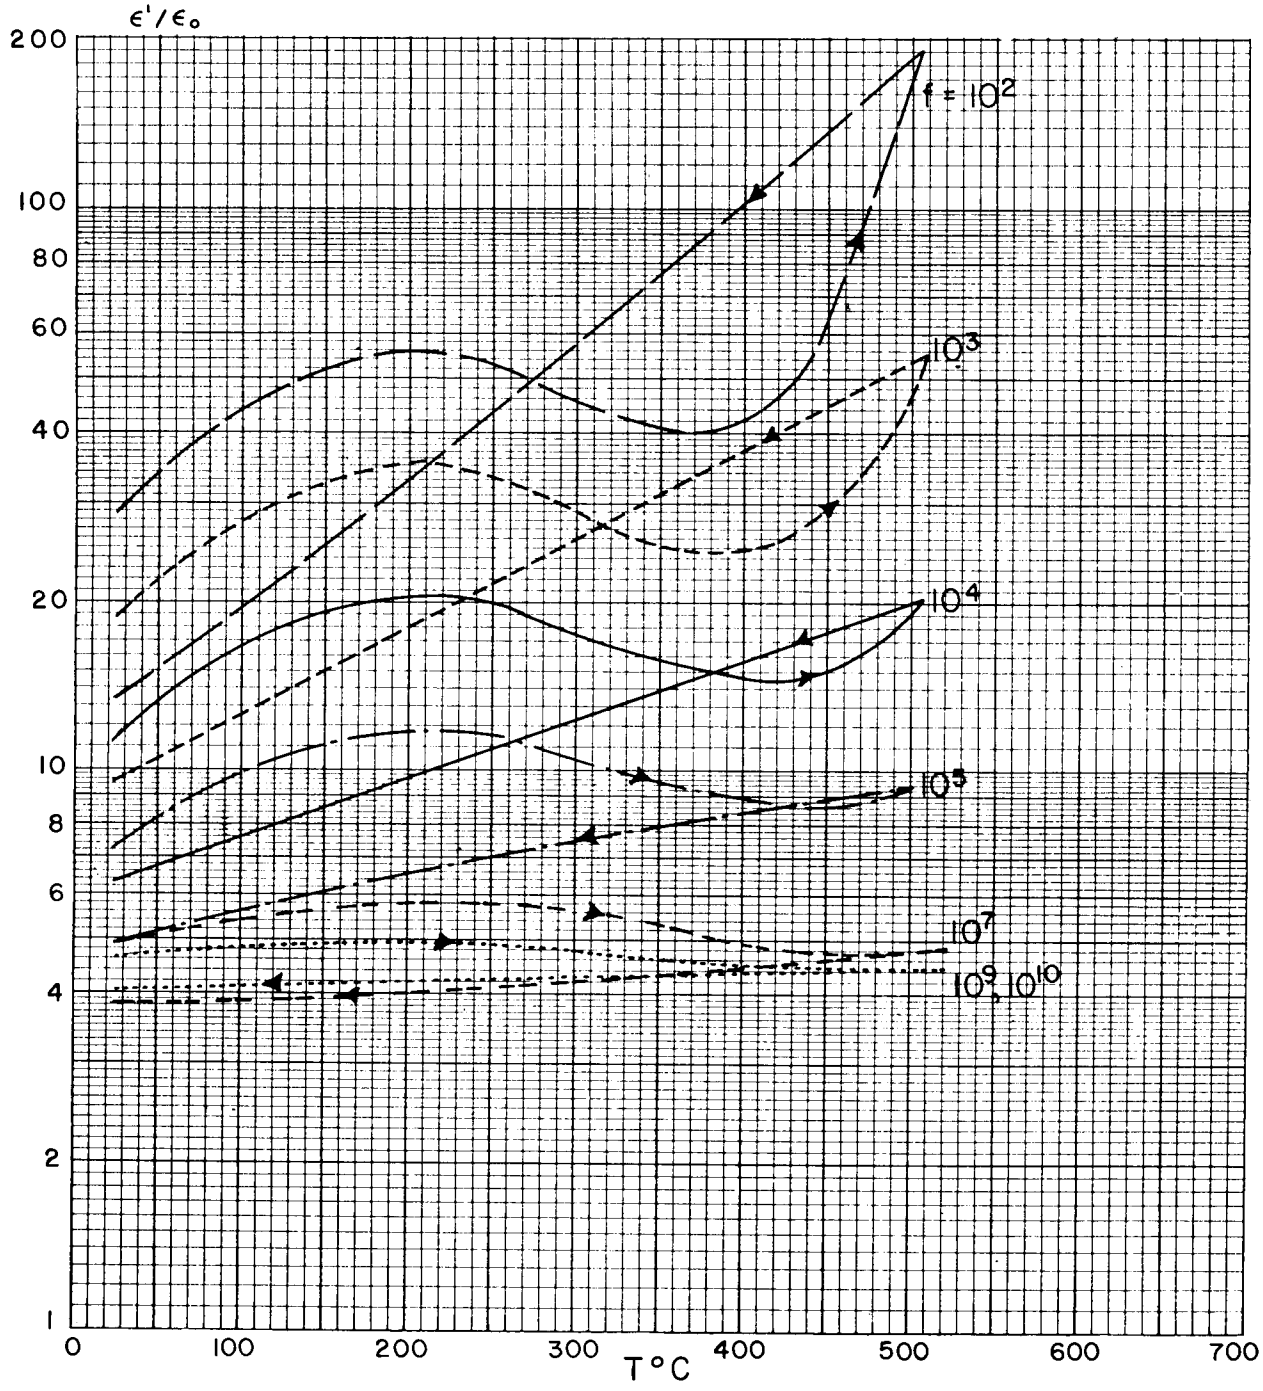

III B 1. Phenolics

Phenolic-asbestos laminate

Goodyear Aircraft Corp.

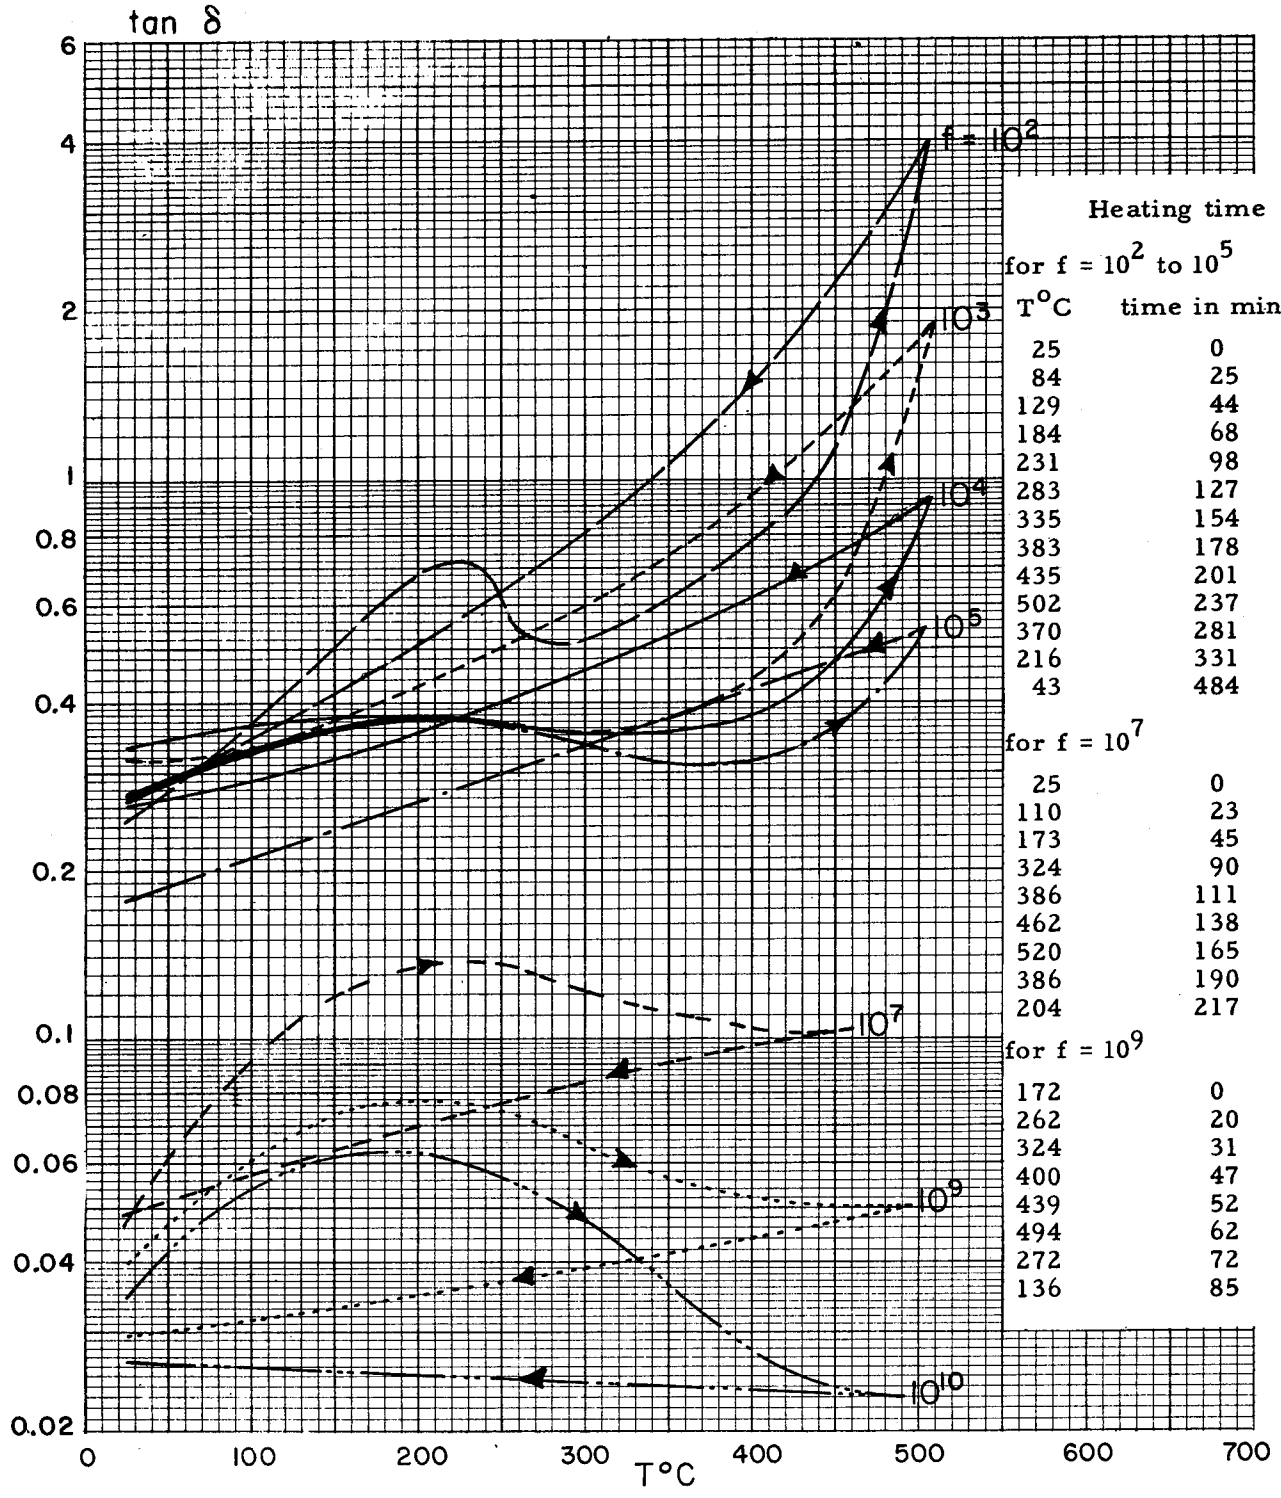

Heating time

for f = 10^2 to 10^5

T°C	time in minutes
25	0
84	25
129	44
184	68
231	98
283	127
335	154
383	178
435	201
502	237
370	281
216	331
43	484

for f = 10^7

25	0
110	23
173	45
324	90
386	111
462	138
520	165
386	190
204	217


for f = 10^9

172	0
262	20
324	31
400	47
439	52
494	62
272	72
136	85

III B 1. Phenolics

Phenolic-"fiberglas"laminate, pressed


Goodyear Aircraft Corp.

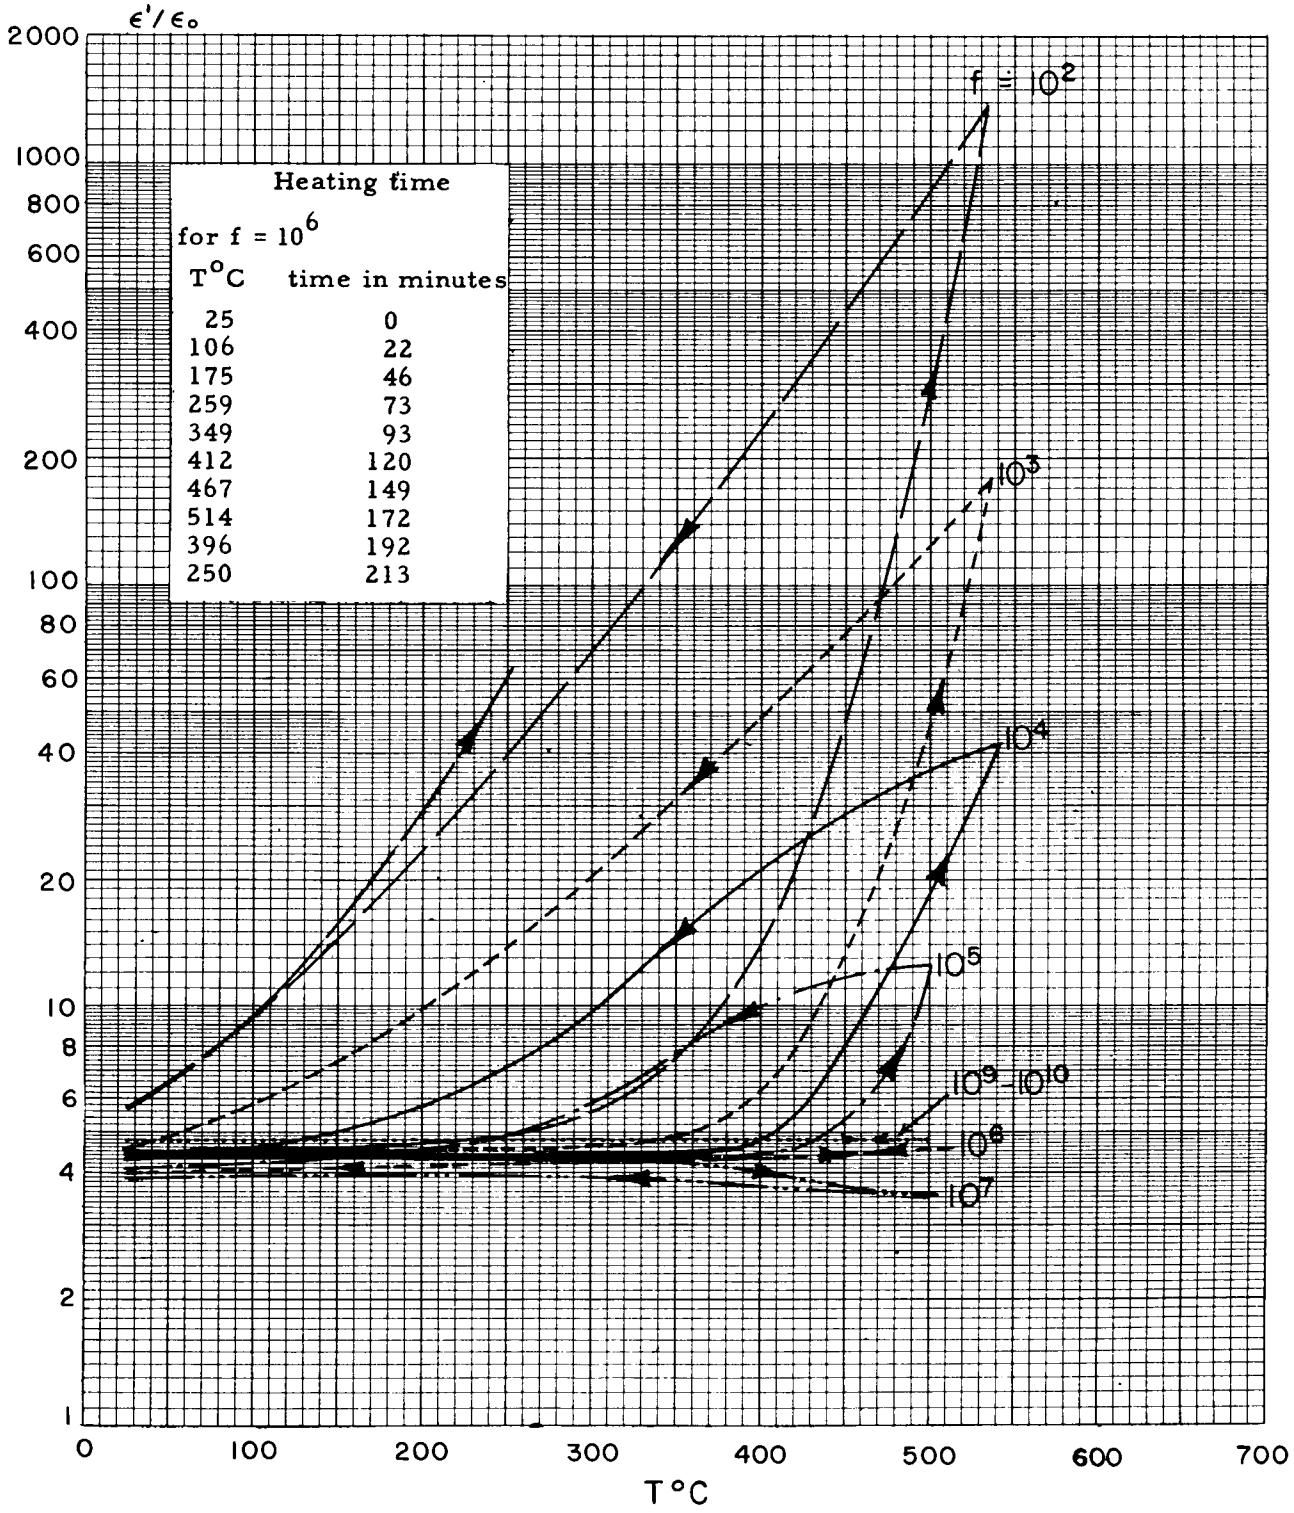

III B 1. Phenolics


Phenolic-"fiberglas"laminate, pressed

Goodyear Aircraft Corp.

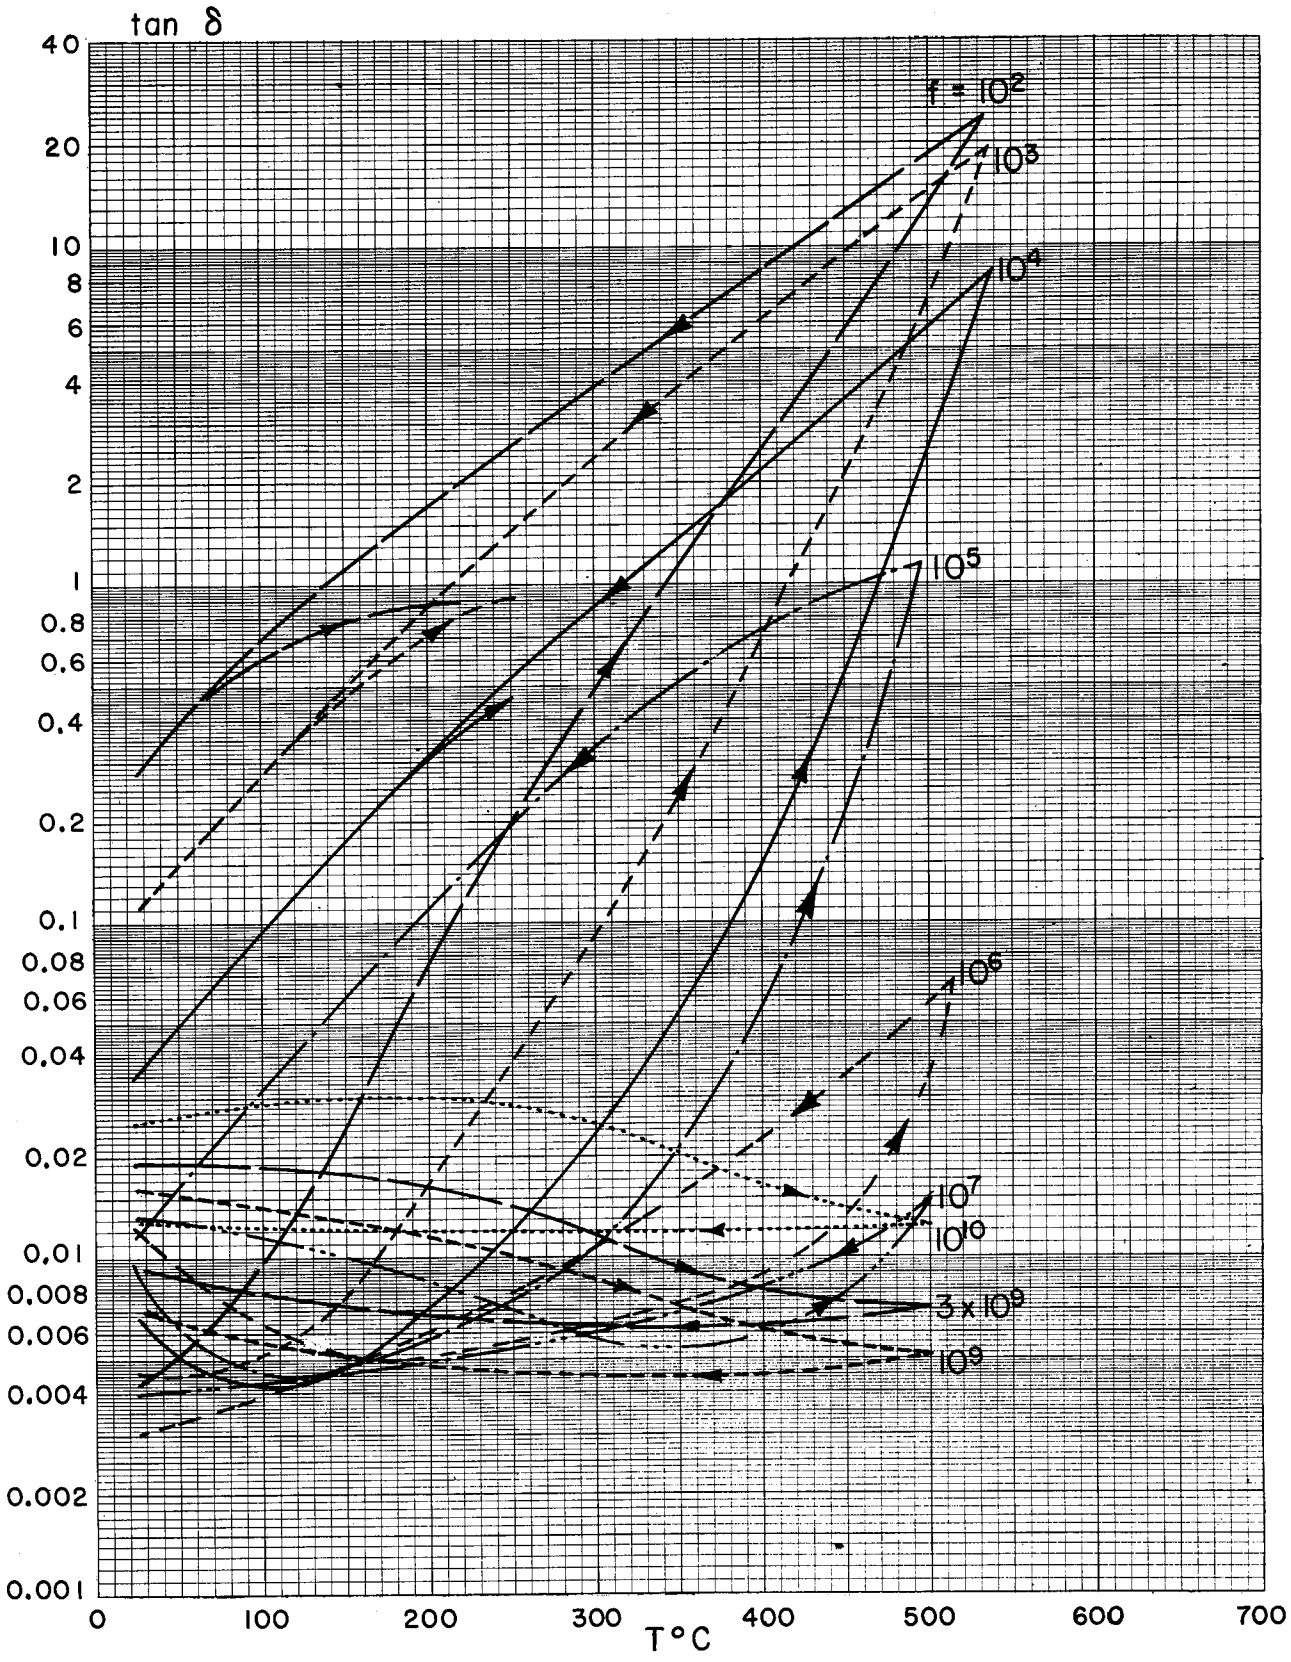


III B 2. Melamine Formaldehyde

"Dilecto" GM-1 Continental Diamond

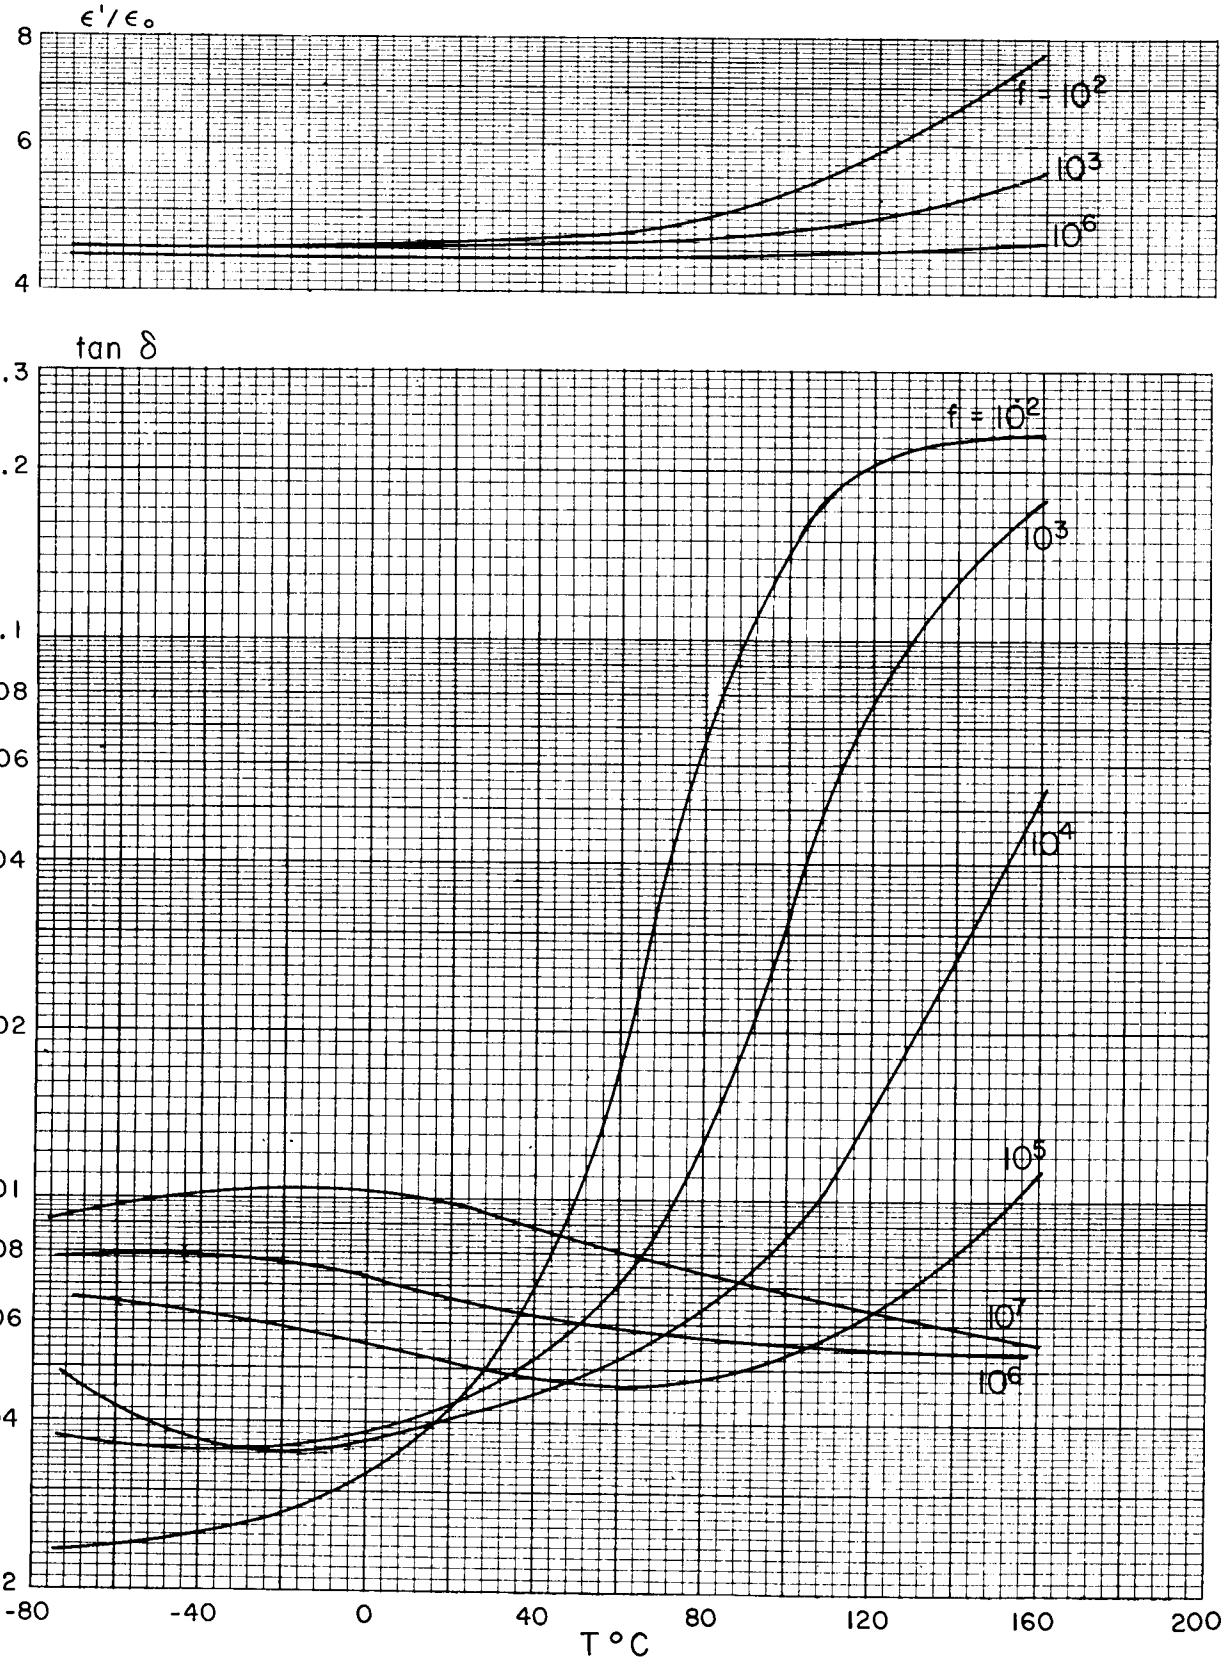


III B 3. Polyamide Resin

"Nylon" FM 10, 001 — du Pont

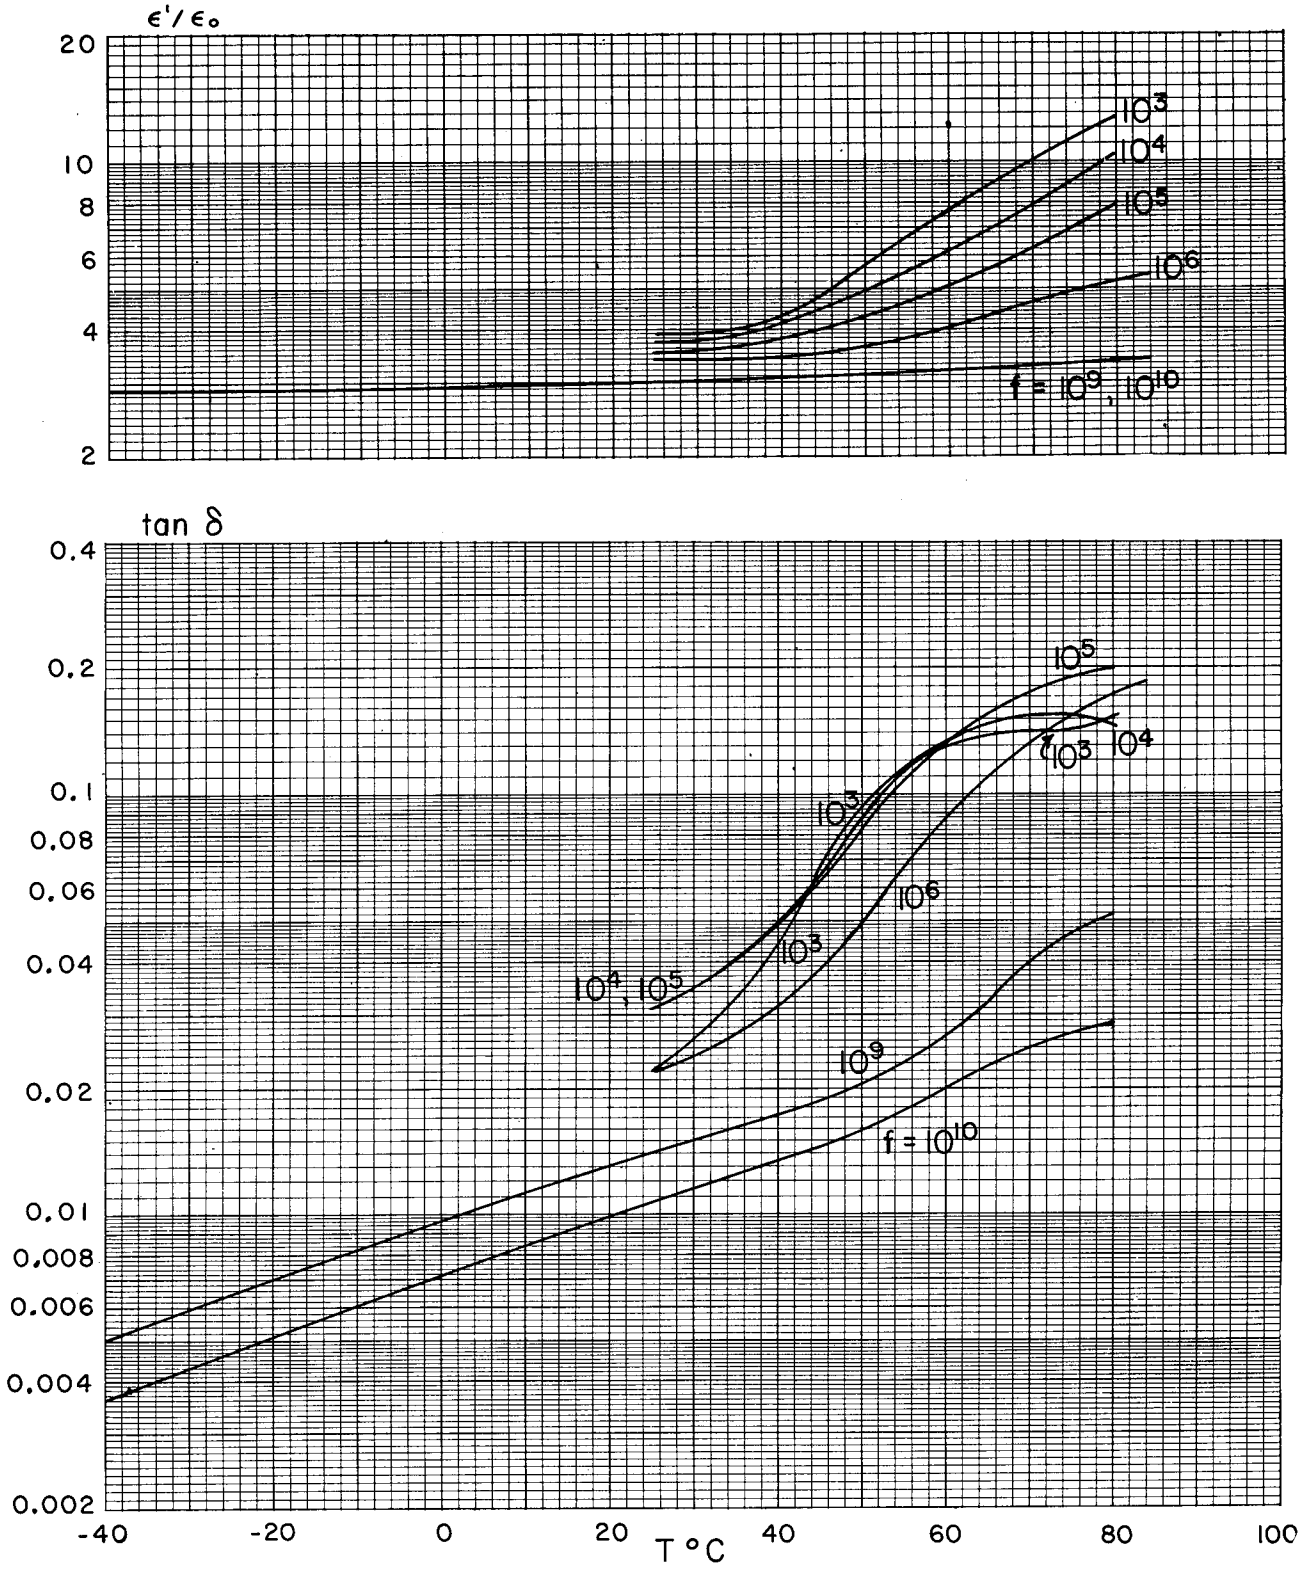


III B 4. Cellulose Derivatives

"Forticel" (No. 28102, 8% plasticizer) Celanese

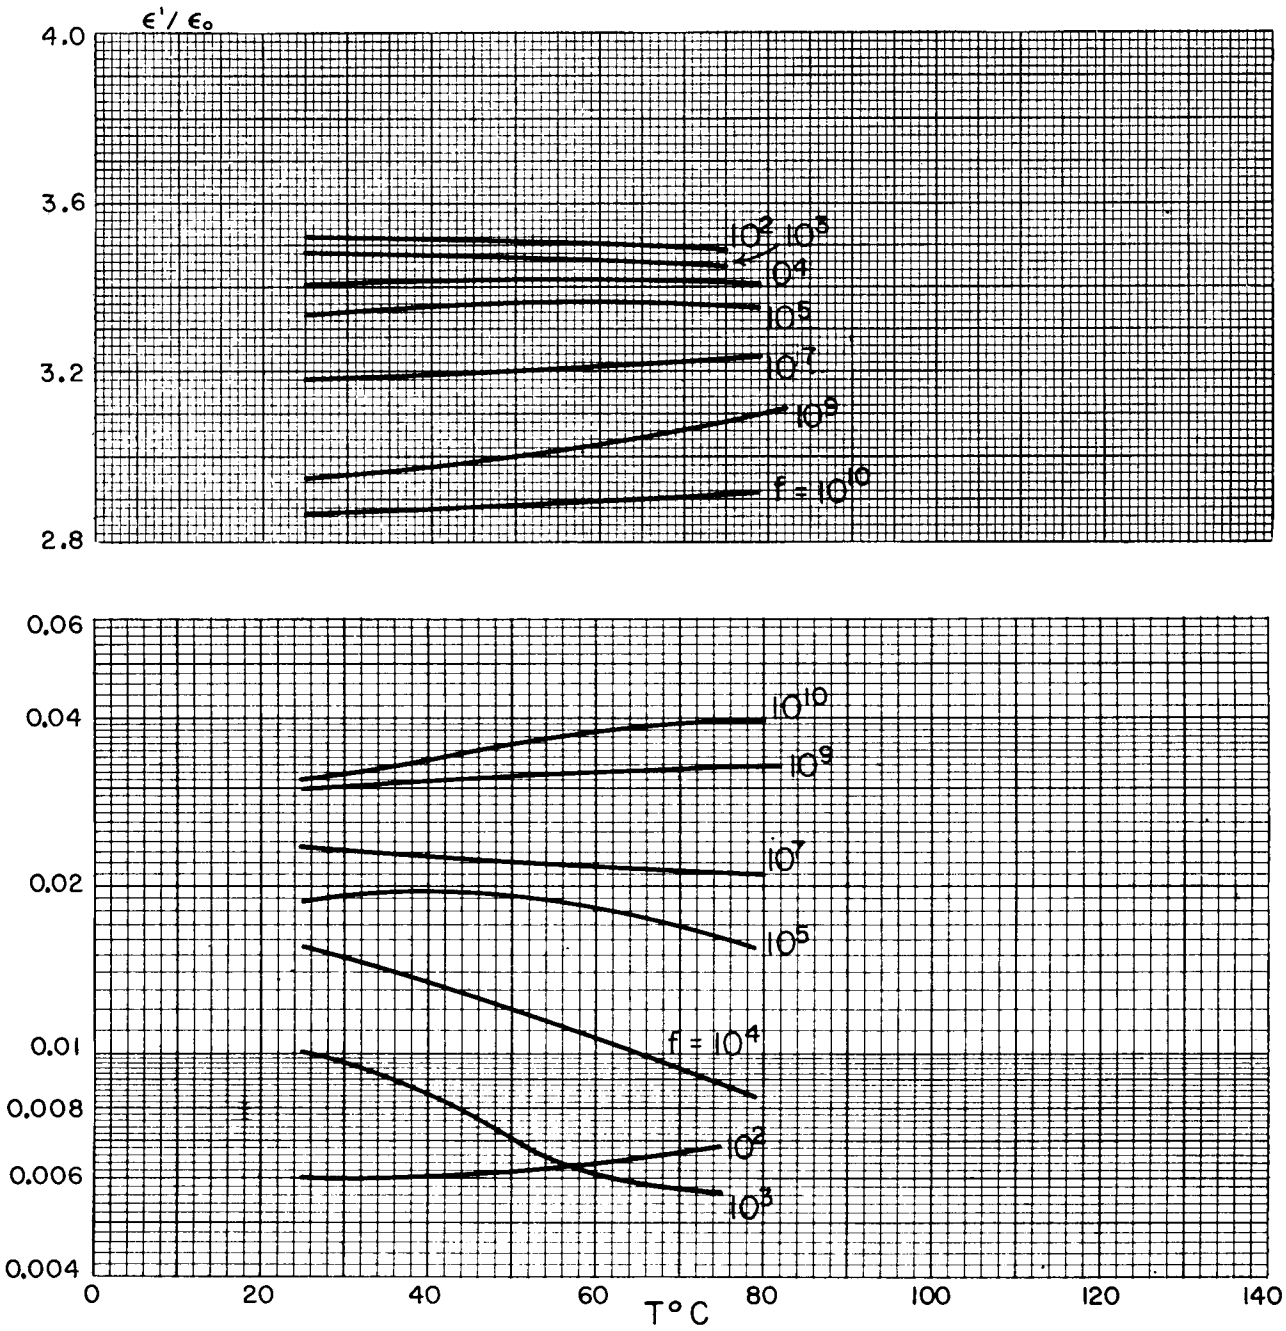


III B 4. Cellulose Derivatives

"Ethocel" LT5 — Dow Chemical

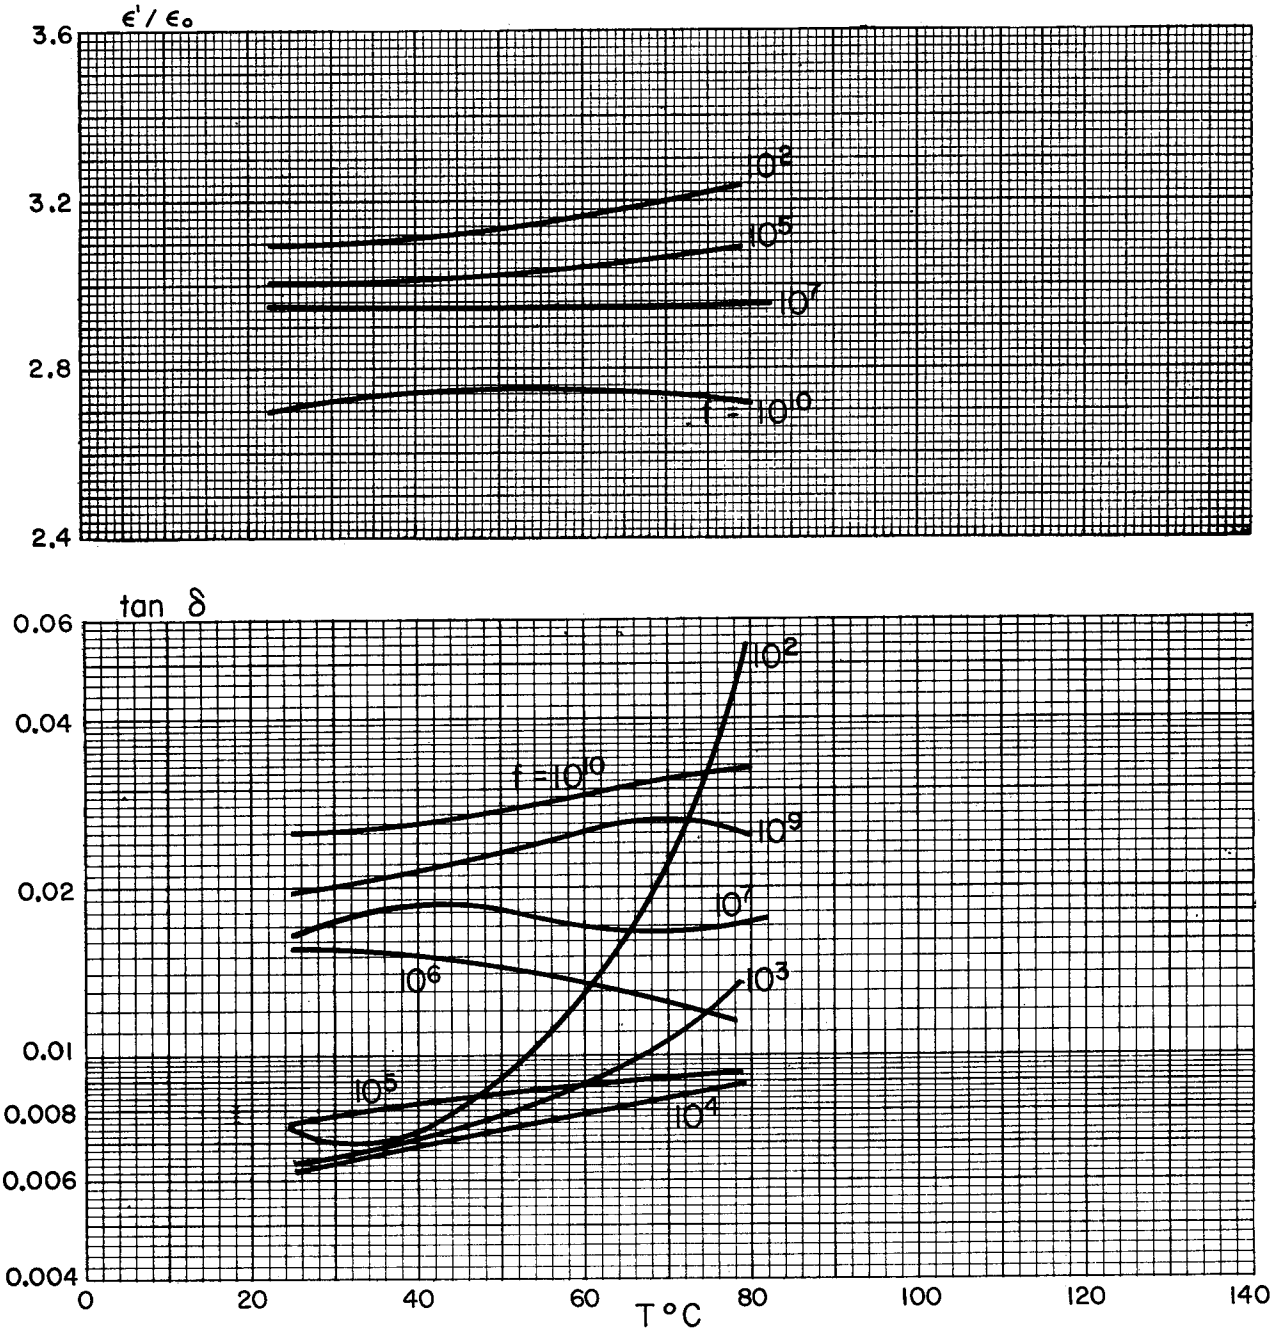


III B 4. Cellulose Derivatives

"CTA" du Pont film dept.

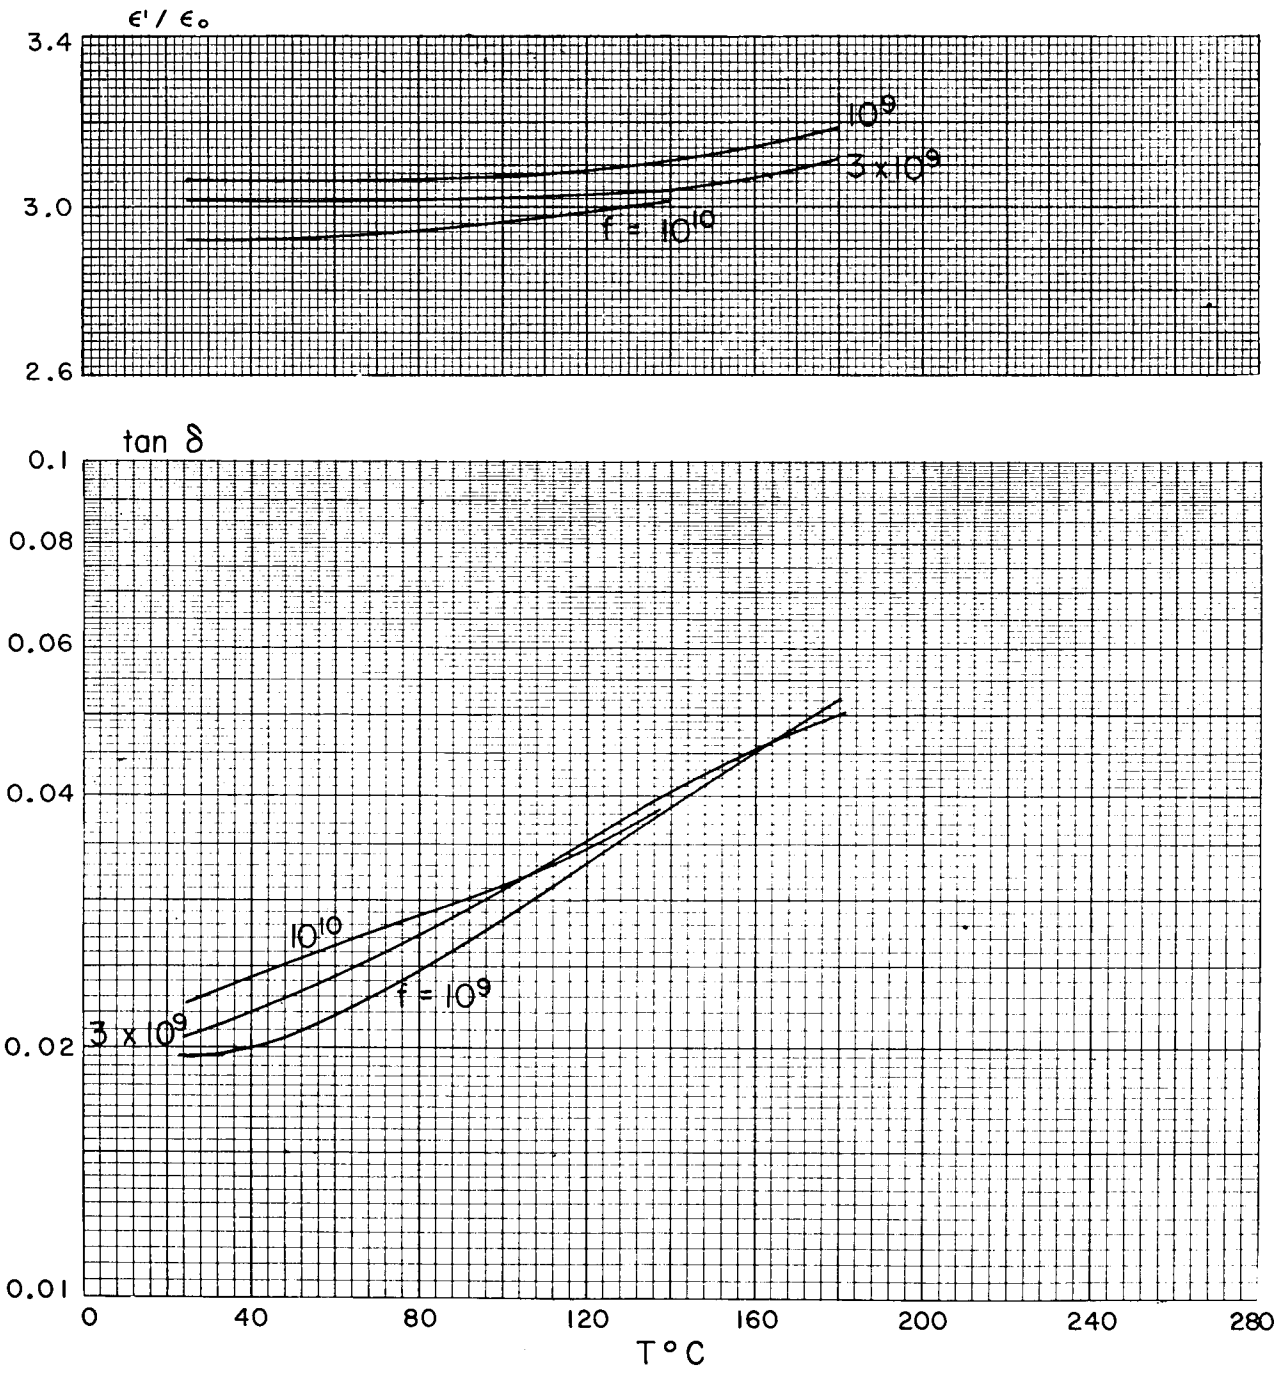


III B 5. Silicone Resins

"Dilecto" (Silicone glass laminate) GB-261S — Continental Diamond

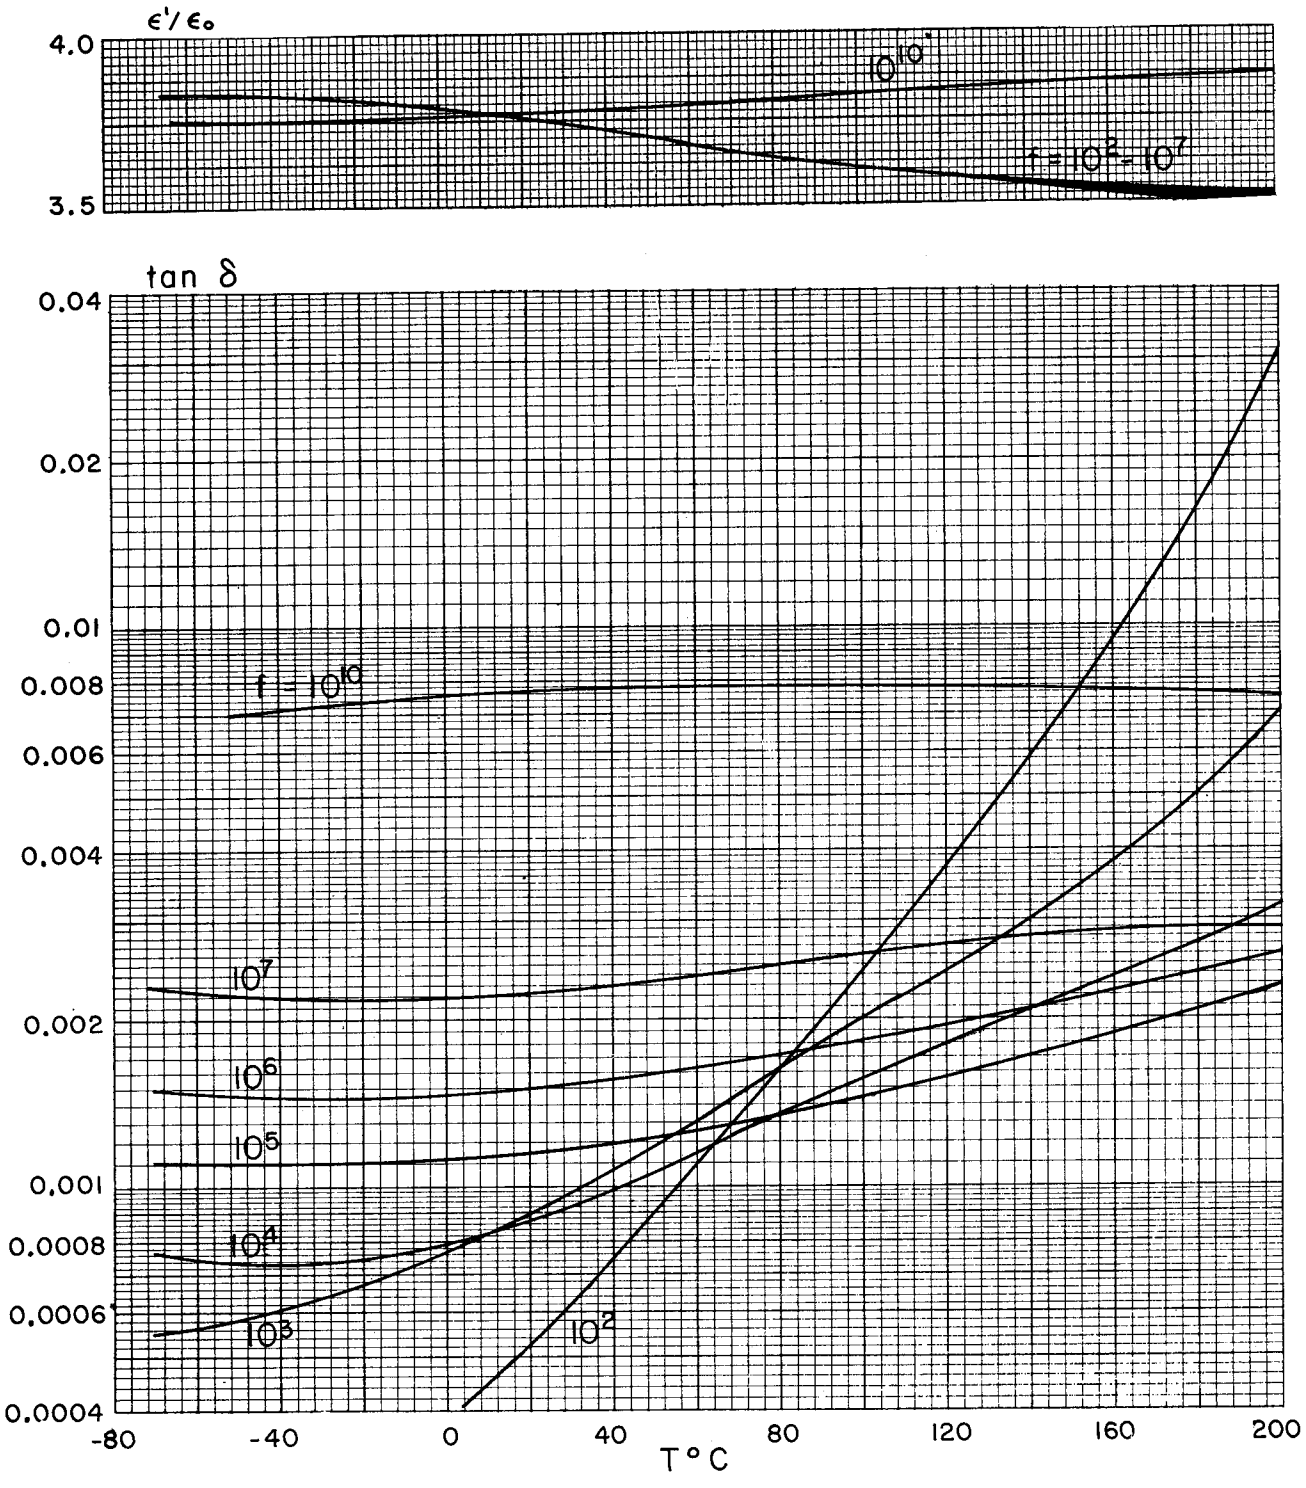


III B 5. Silicone Resins

DC 301 Molding Compound — Dow Corning

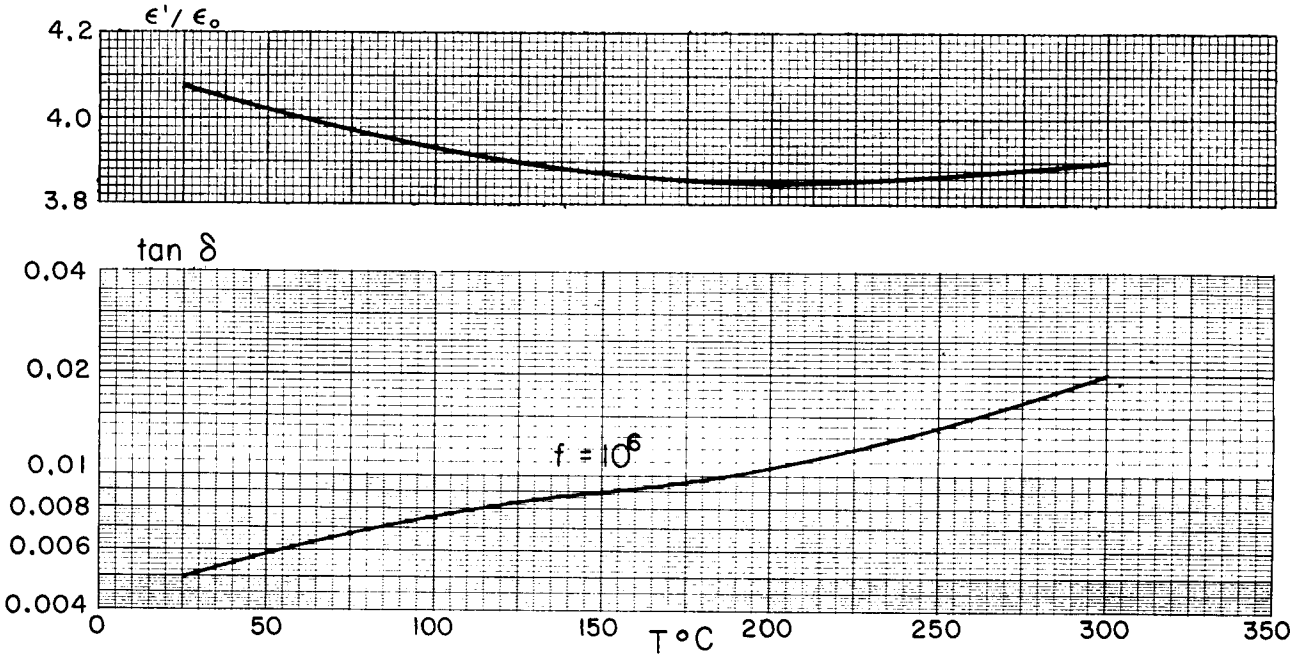


Dow Corning 2105 "Fiberglas" laminate — Dow Corning

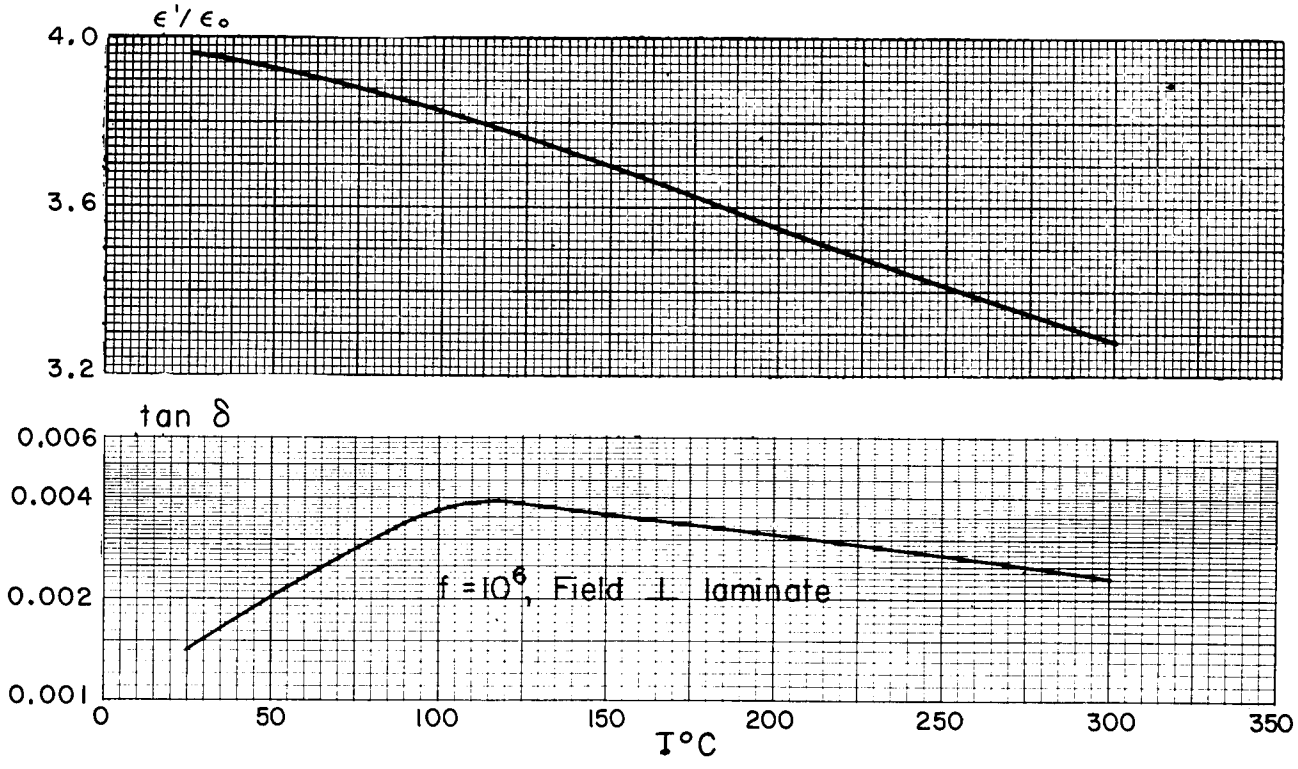

III B 5. Silicone Resins


Dow Corning 2106 "Fiberglas" laminate

Dow Corning

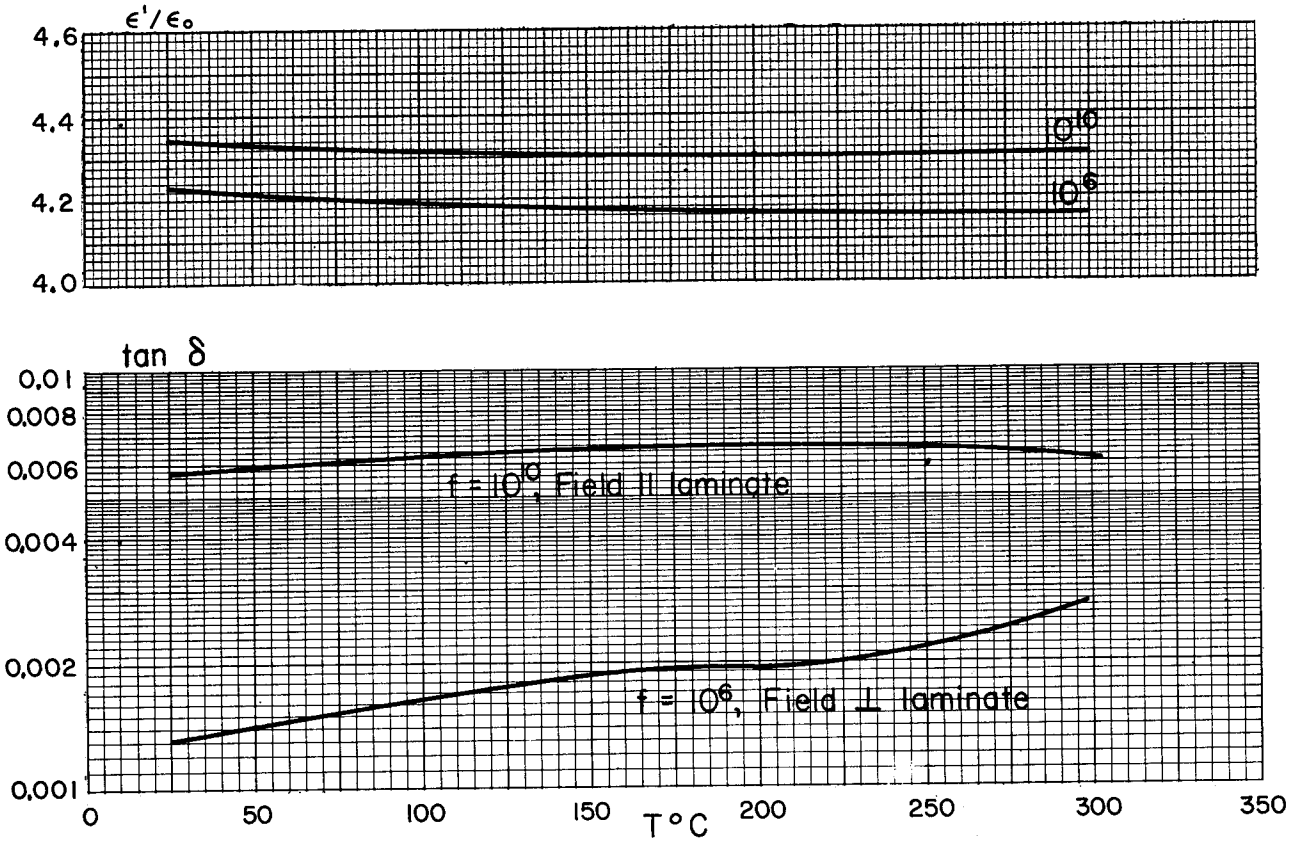

III B 5. Silicone Resins


Silicone-asbestos laminate — Goodyear Aircraft Corp.

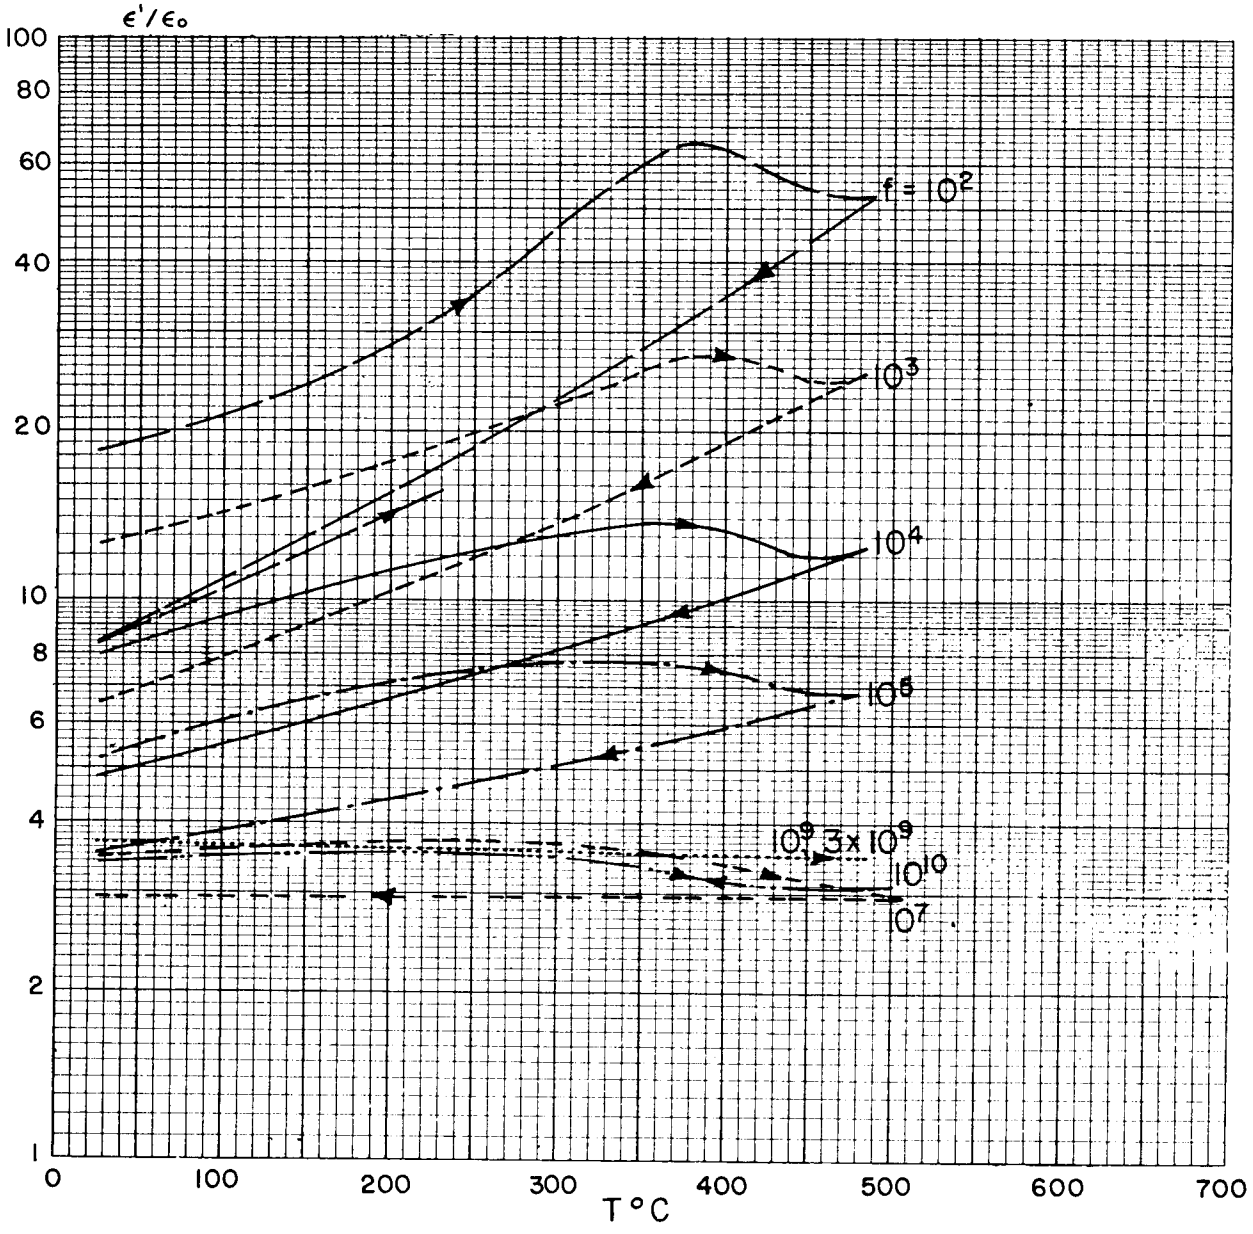

III B 5. Silicone Resins

Silicone-asbestos laminate

Goodyear Aircraft Corp.

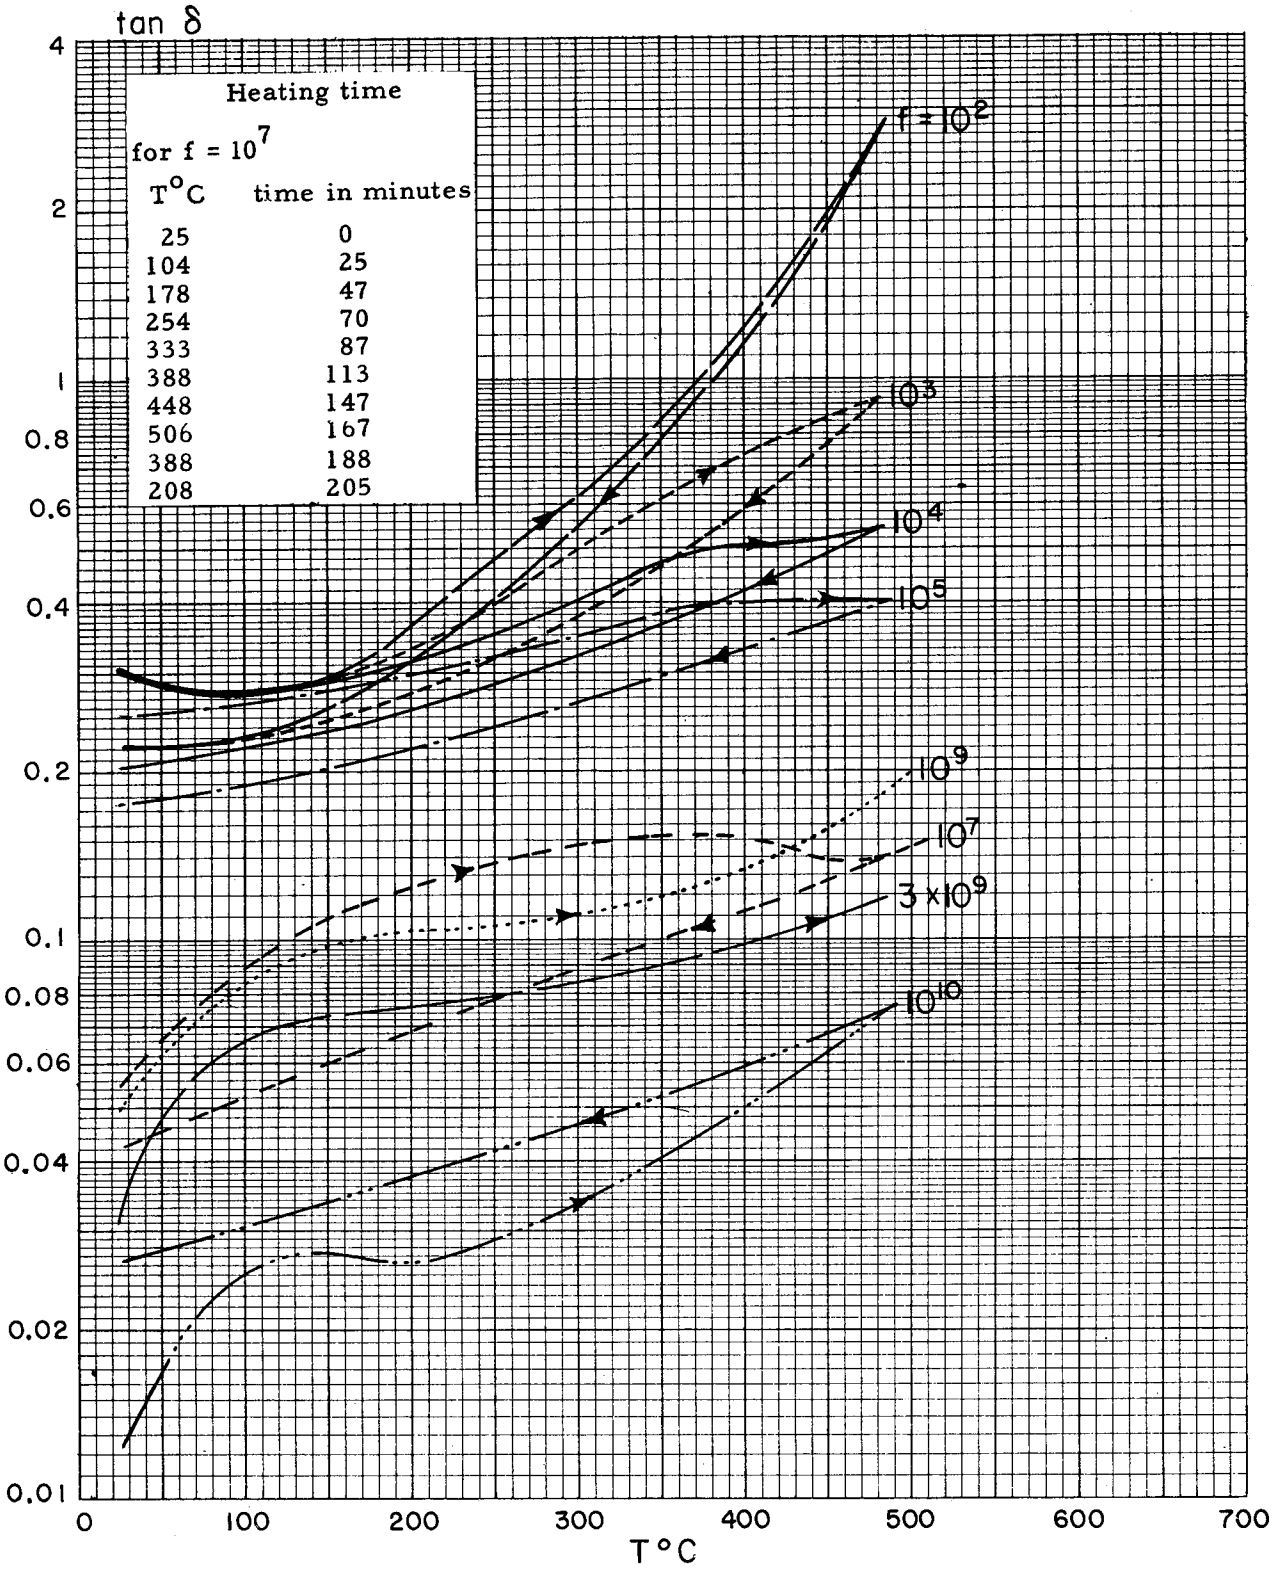


Heating time for $f = 10^7$

T°C	time in minutes
25	0
104	25
178	47
254	70
333	87
388	113
448	147
506	167
388	188
208	205


III B 5. Silicone Resins

Silicone-"fiberglas" laminate, pressed — Goodyear Aircraft Corp.

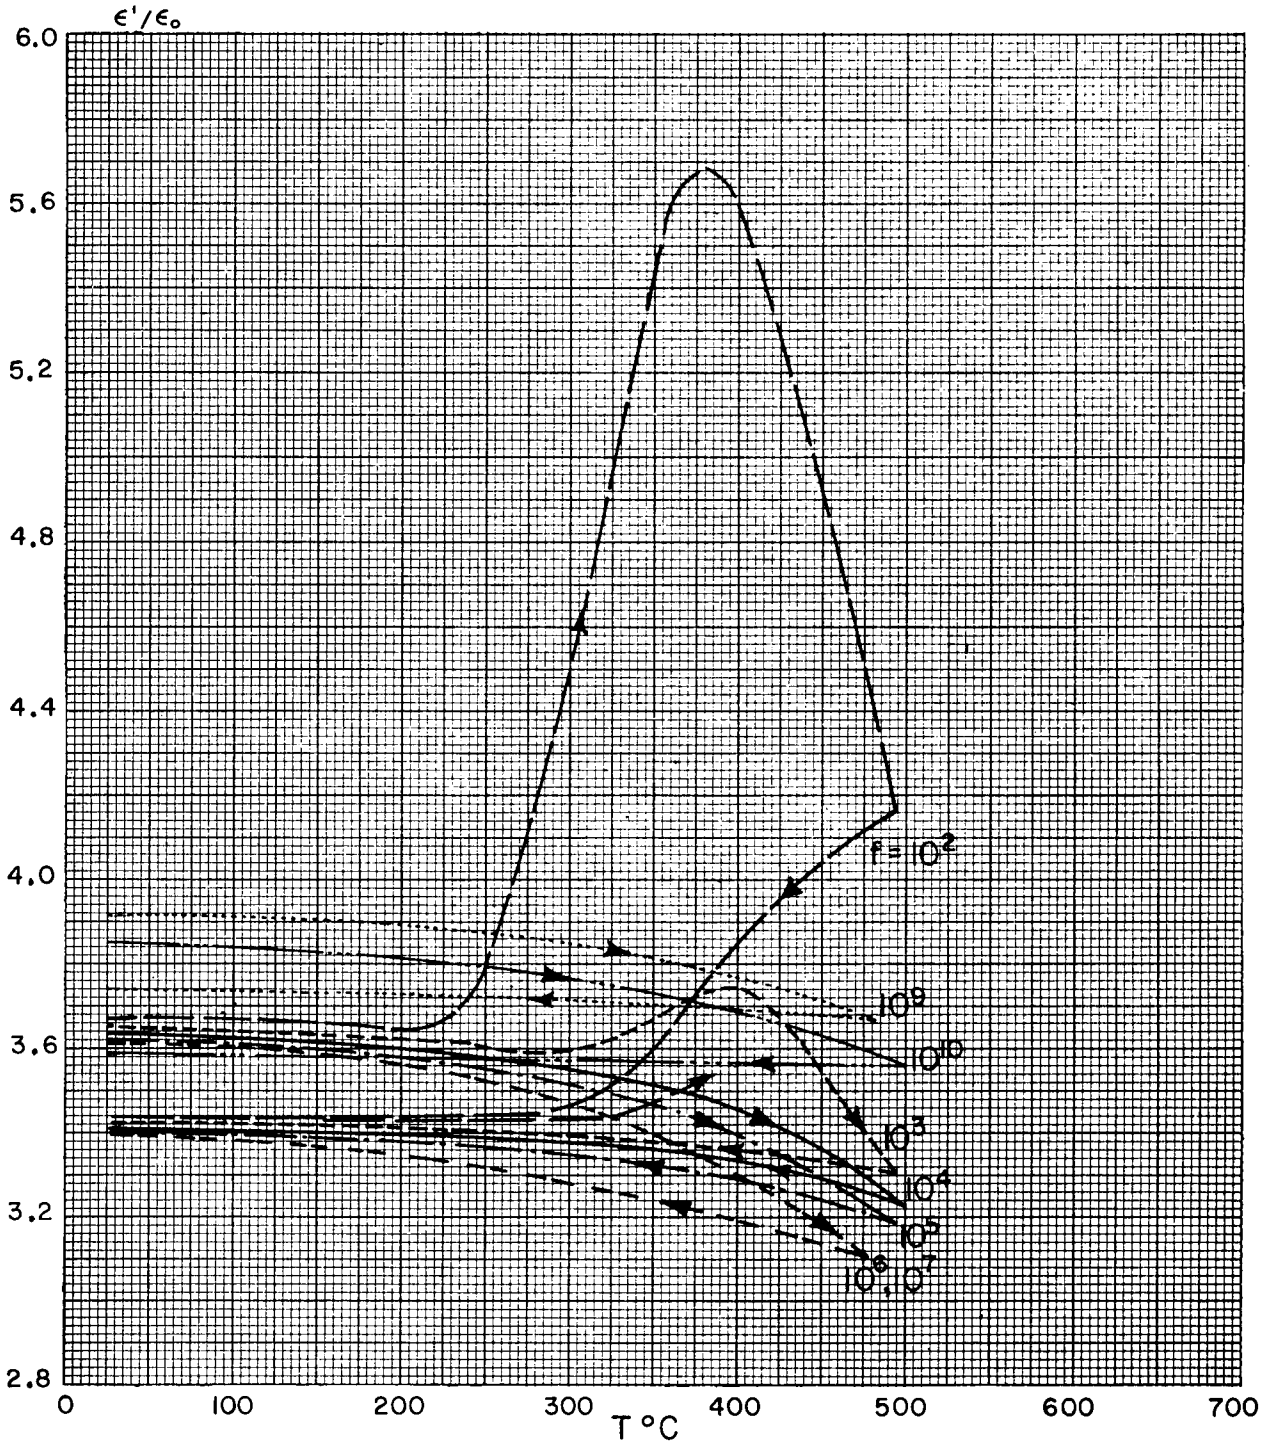

III B 5. Silicone Resins

Silicone-"fiberglas" laminate, pressed — Goodyear Aircraft Corp.

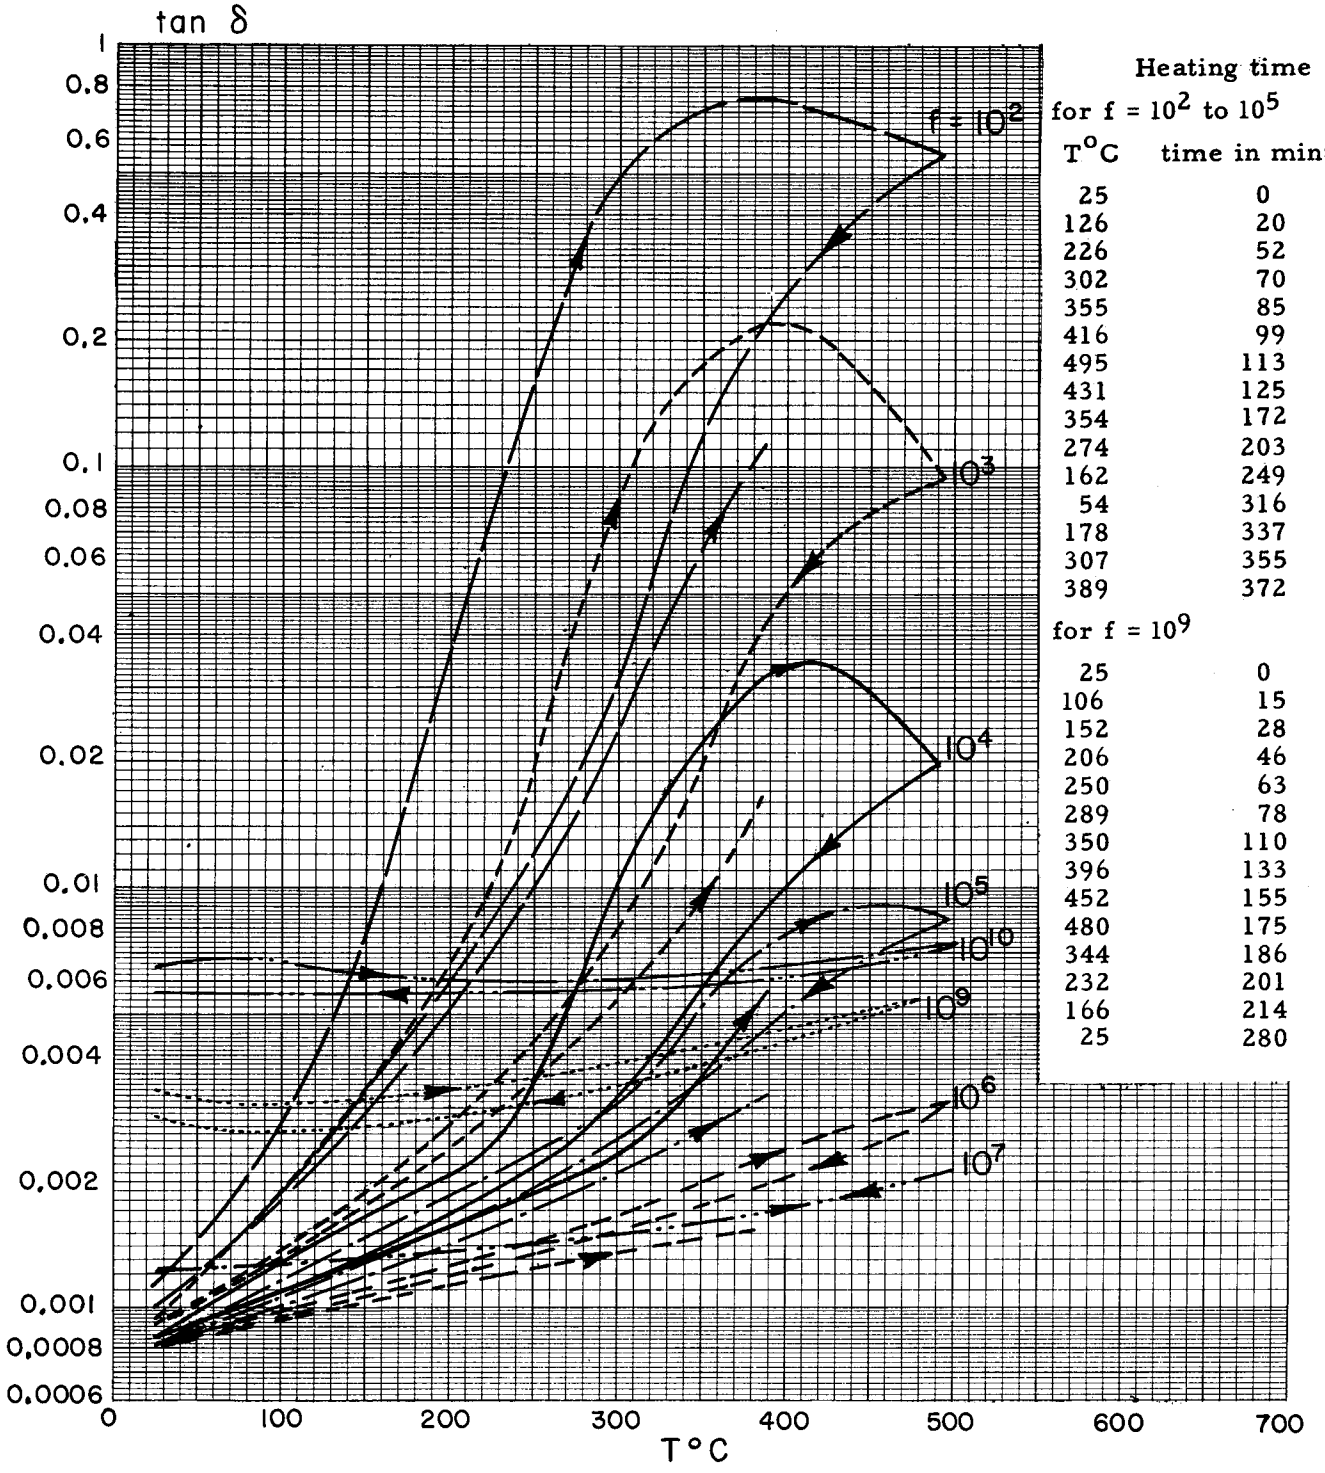

Heating time for $f = 10^2$ to 10^5


T°C	time in minutes
25	0
126	20
226	52
302	70
355	85
416	99
495	113
431	125
354	172
274	203
162	249
54	316
178	337
307	355
389	372

for $f = 10^9$


25	0
106	15
152	28
206	46
250	63
289	78
350	110
396	133
452	155
480	175
344	186
232	201
166	214
25	280

III B 5. Silicone Resins

Silicone-"fiberglas" laminate, bagged — Goodyear Aircraft Corp.

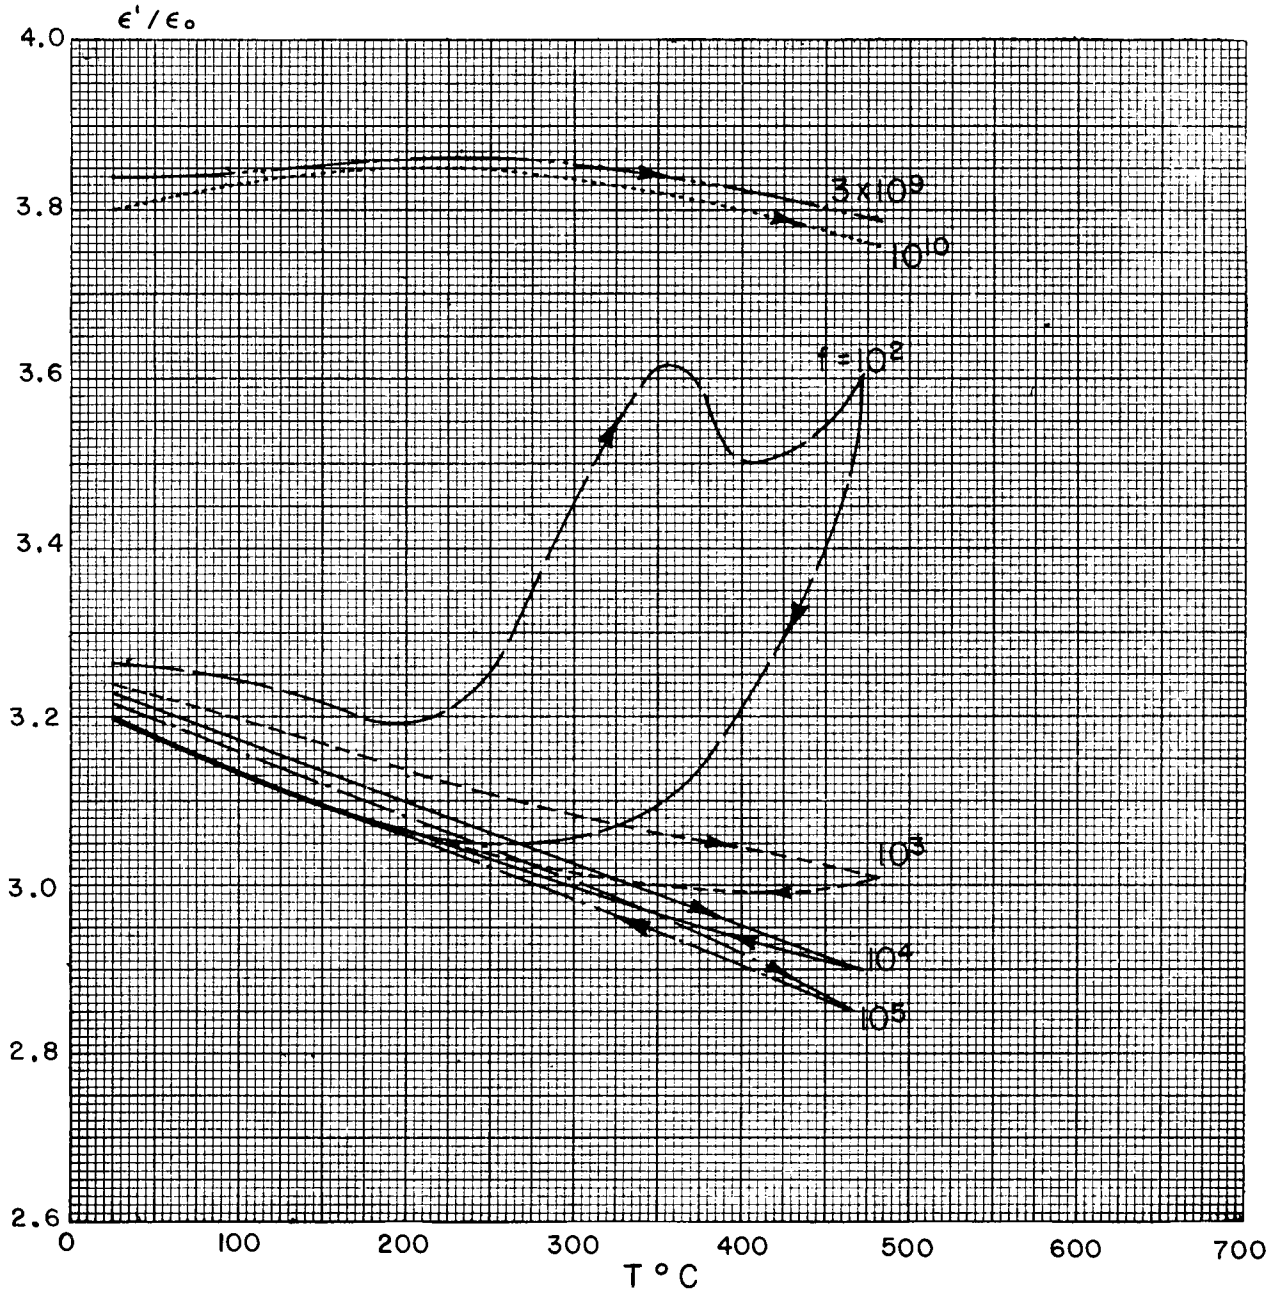


Silicone-"fiberglas" laminate, bagged — Goodyear Aircraft Corp.

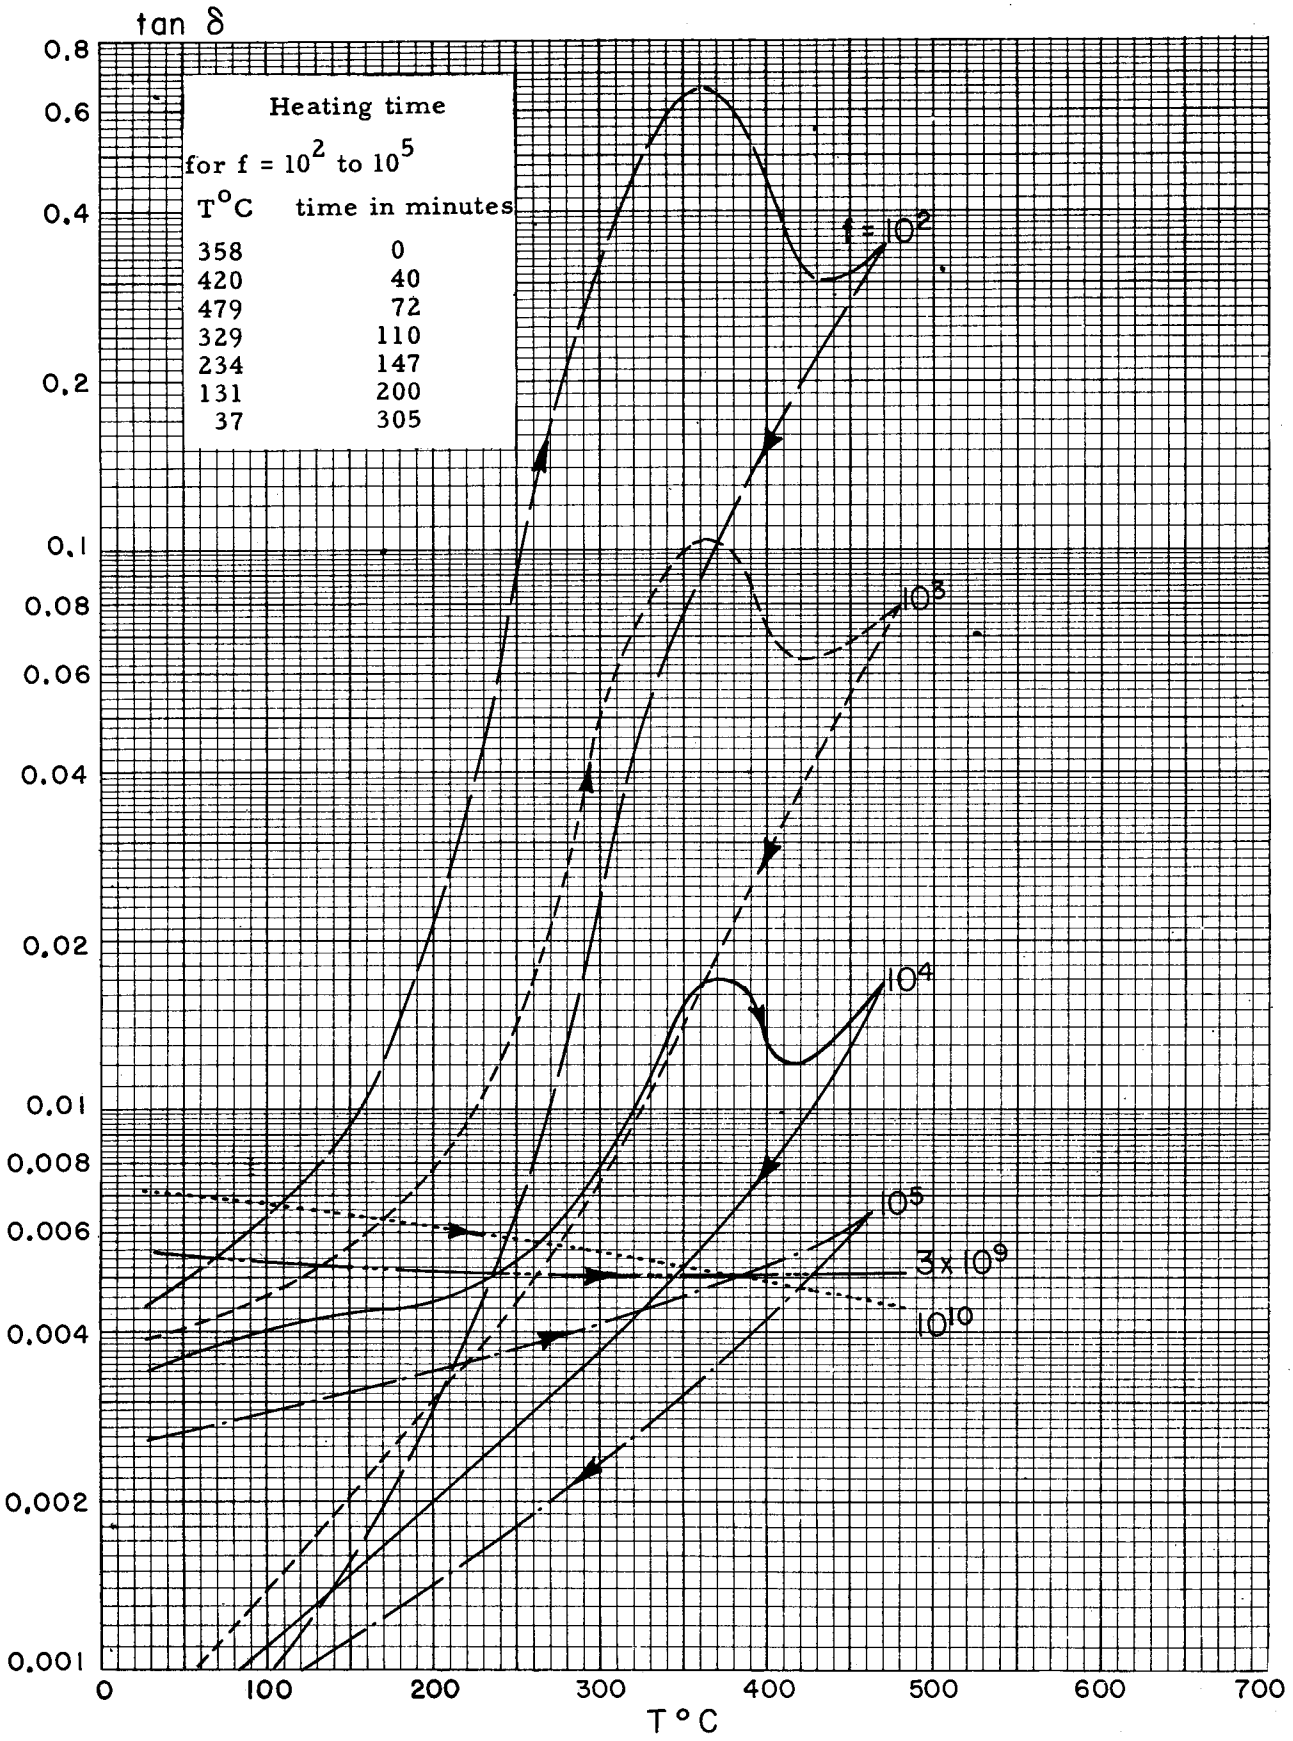


III B 6. Polychlorotrifluoroethylene

"Kel-F" X-200 M. W. Kellogg

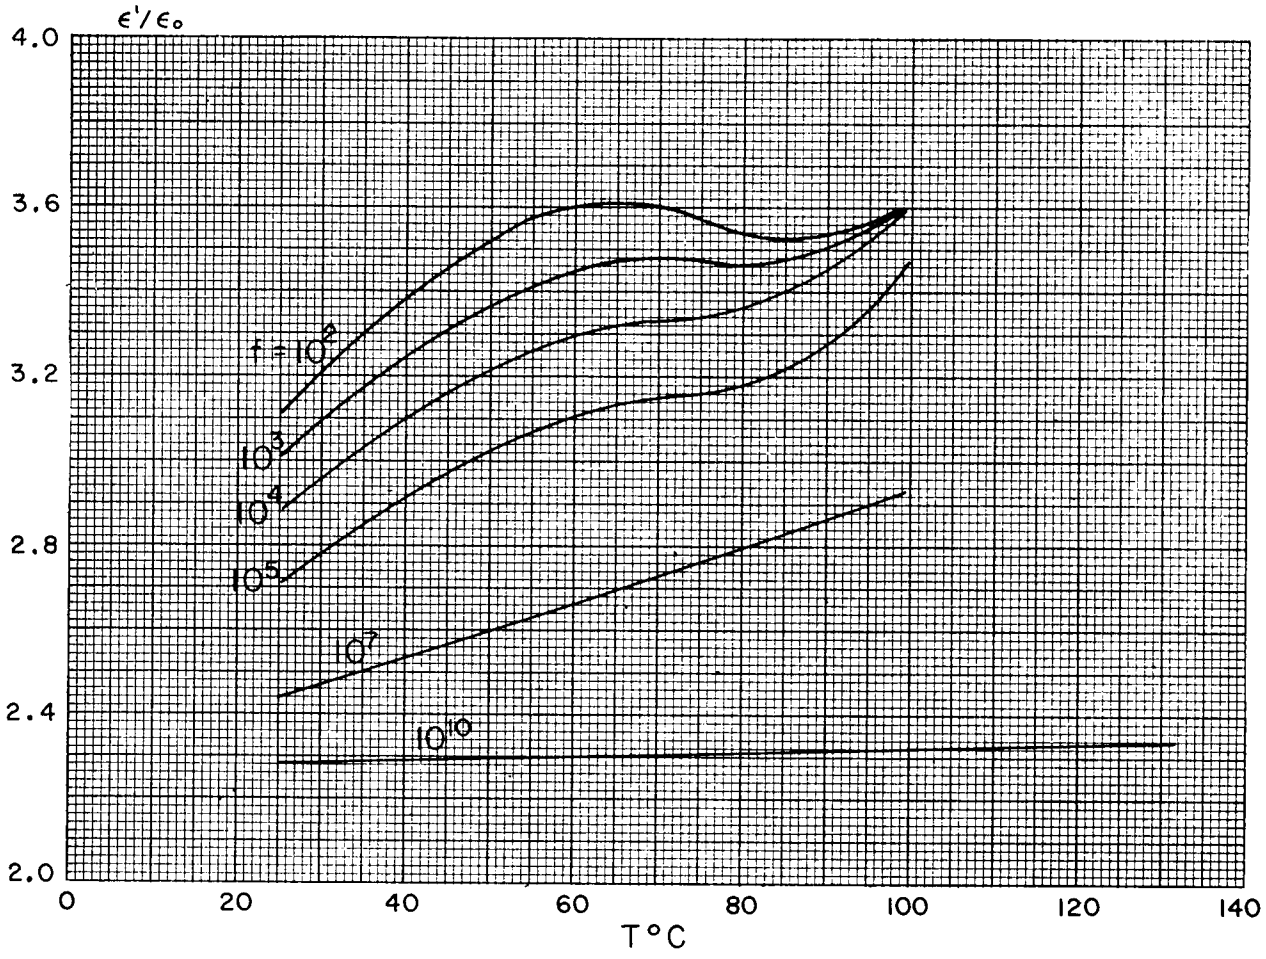


III B 6. Polychlorotrifluoroethylene

"Kel-F" X-200 — M. W. Kellogg

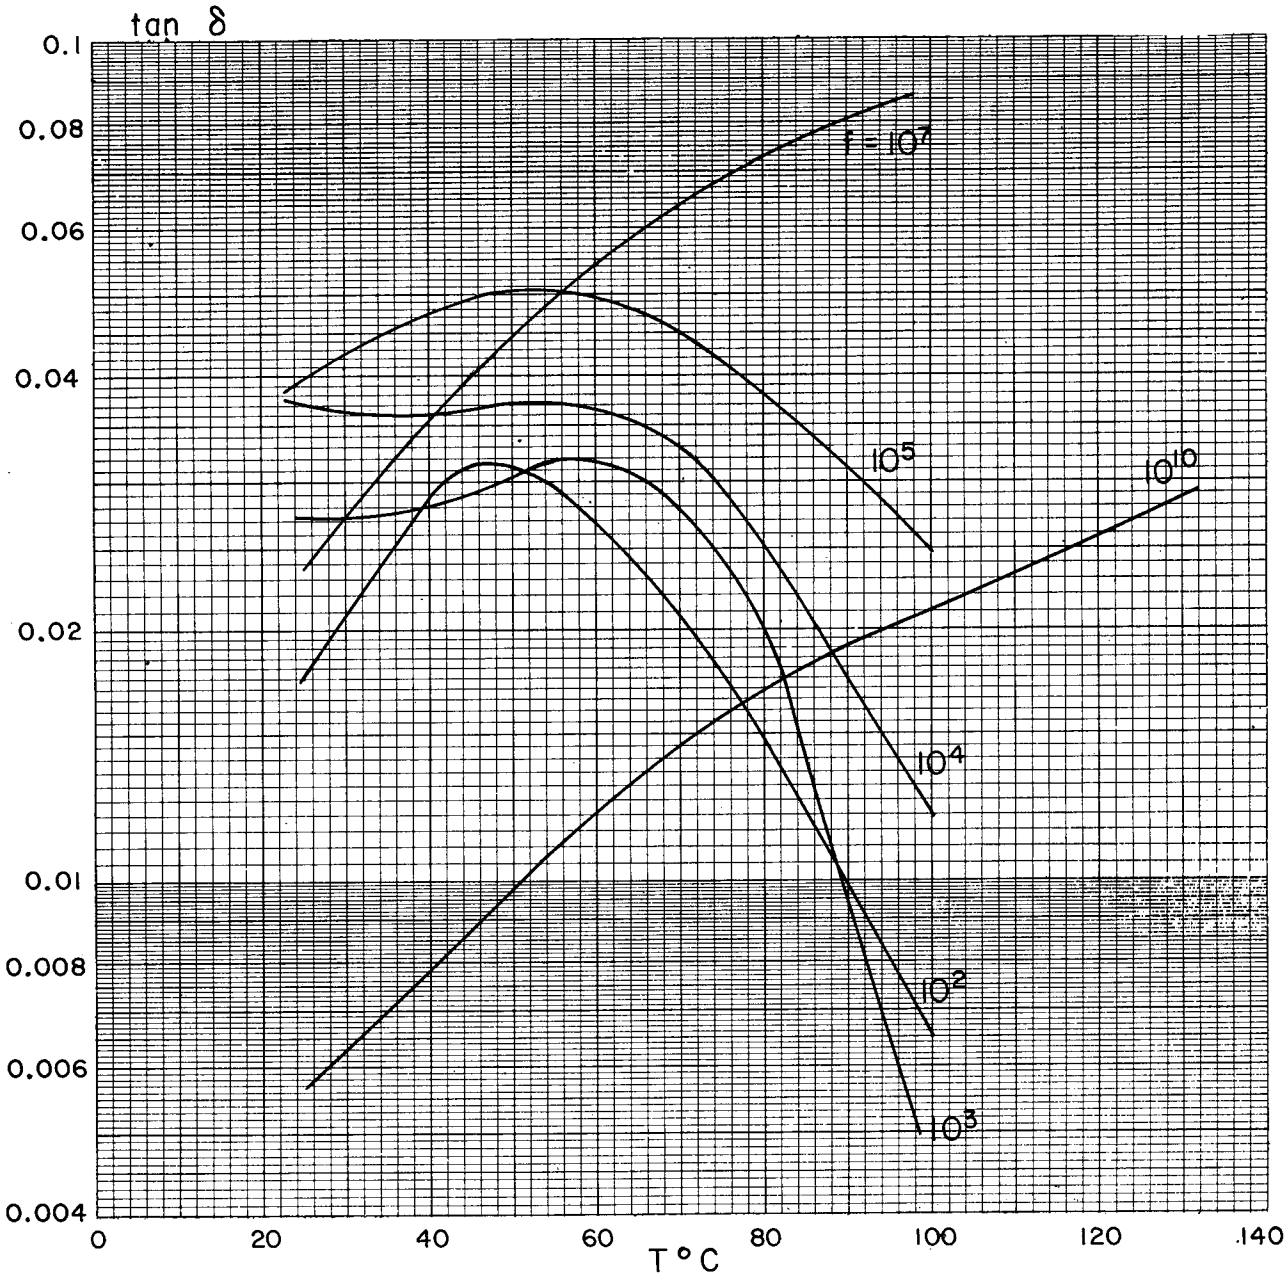

III B 7. Polytetrafluoroethylene


"Dilecto" ("Teflon" laminate) GB-112T — Continental Diamond

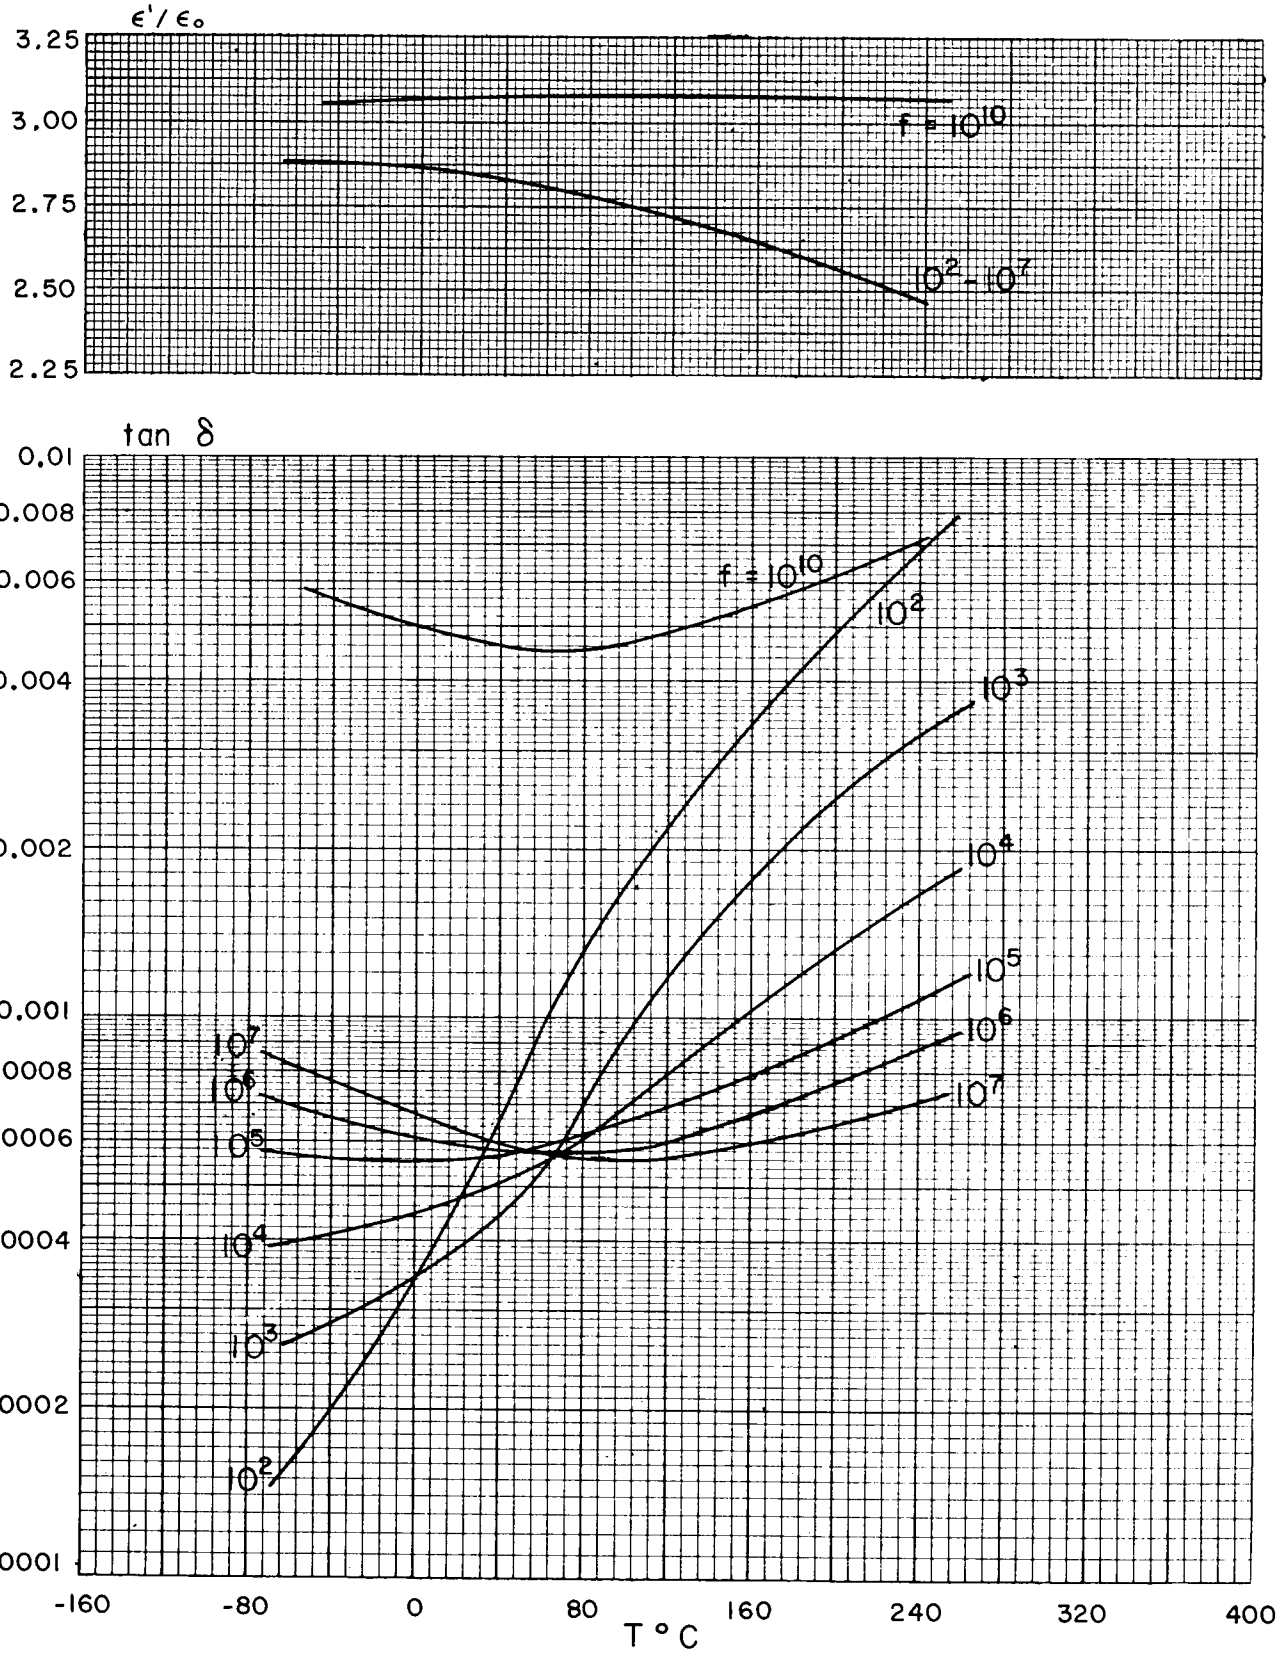

III B 8. Styrene Copolymers

"Rexolite" 1422


Rex Plastics

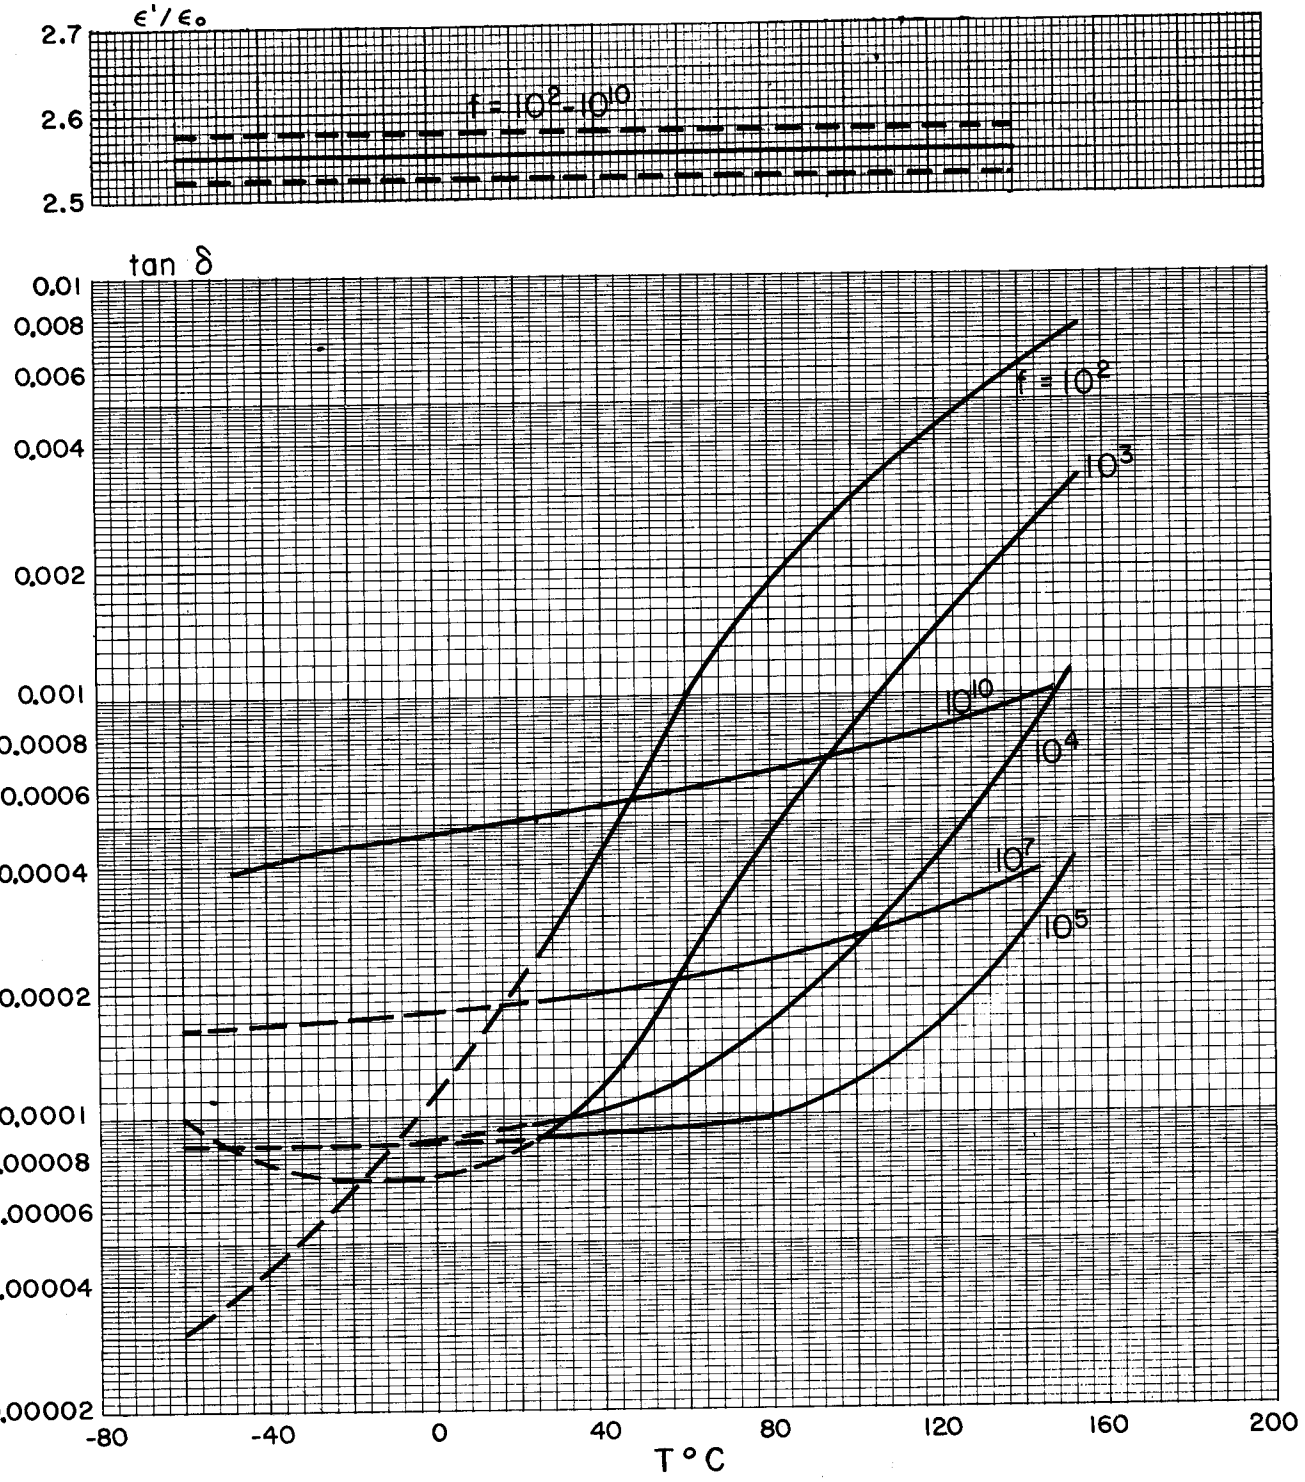

III B 9. Polyesters

"Laminac" 4232 - glass mat


American Cyanamid

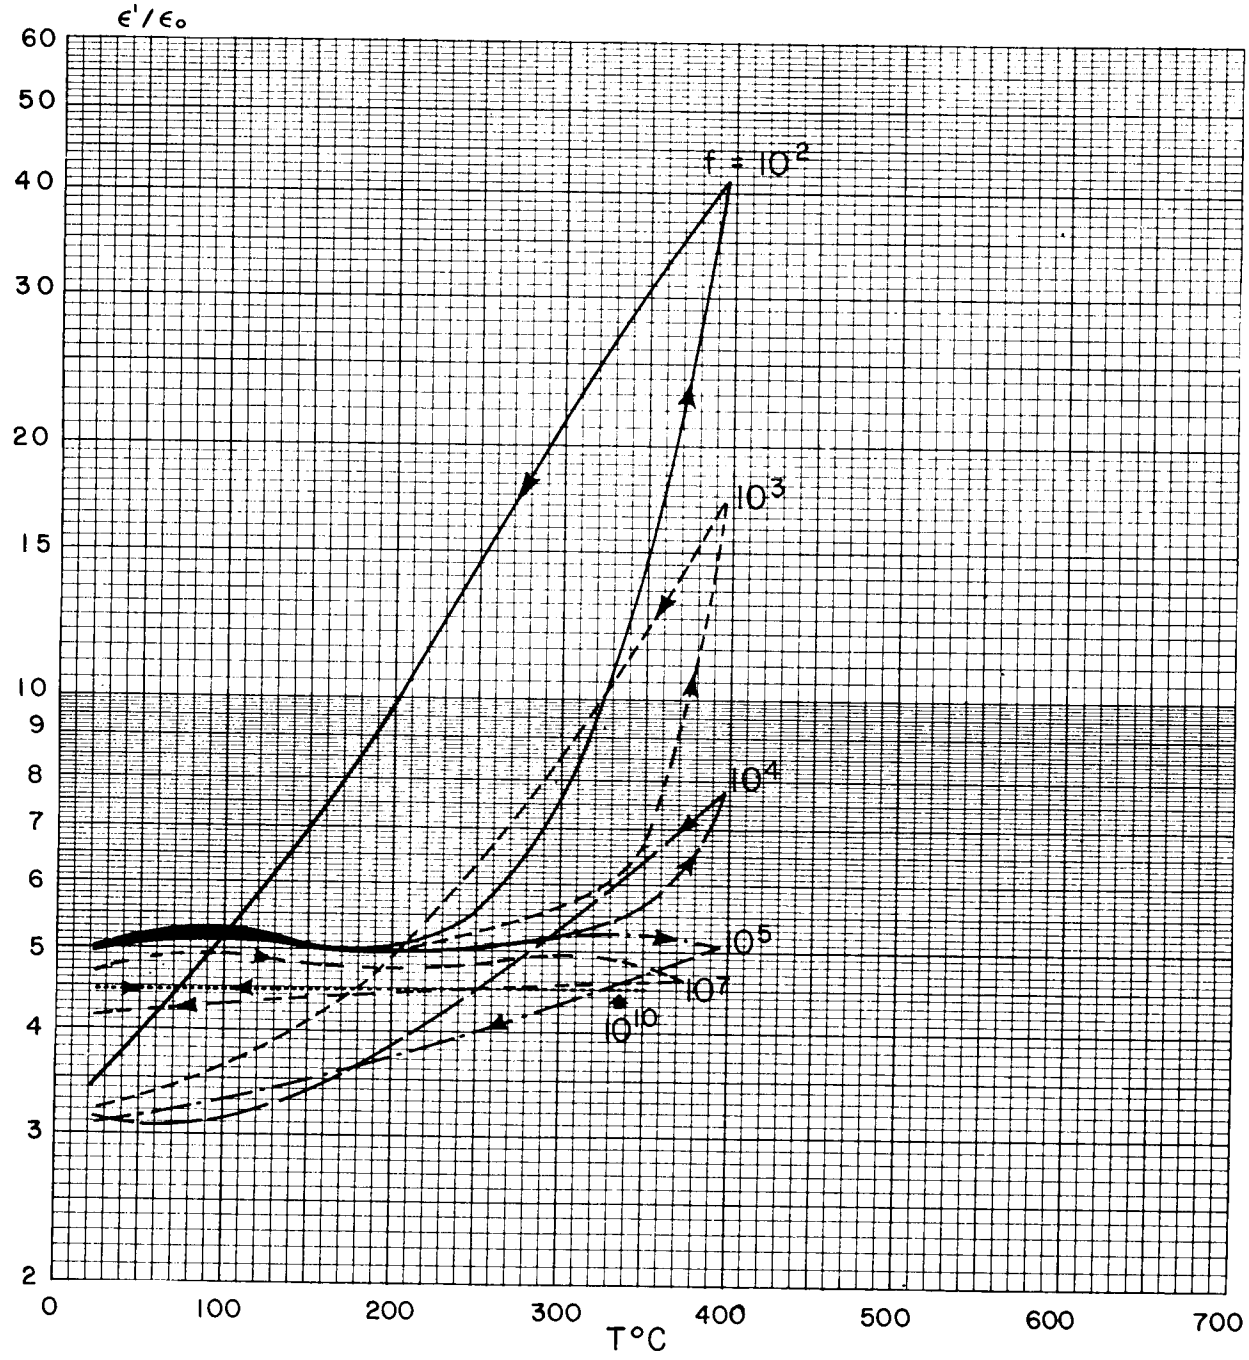

III B 9. Polyesters

"Laminac" 4232 - glass mat

American Cyanamid

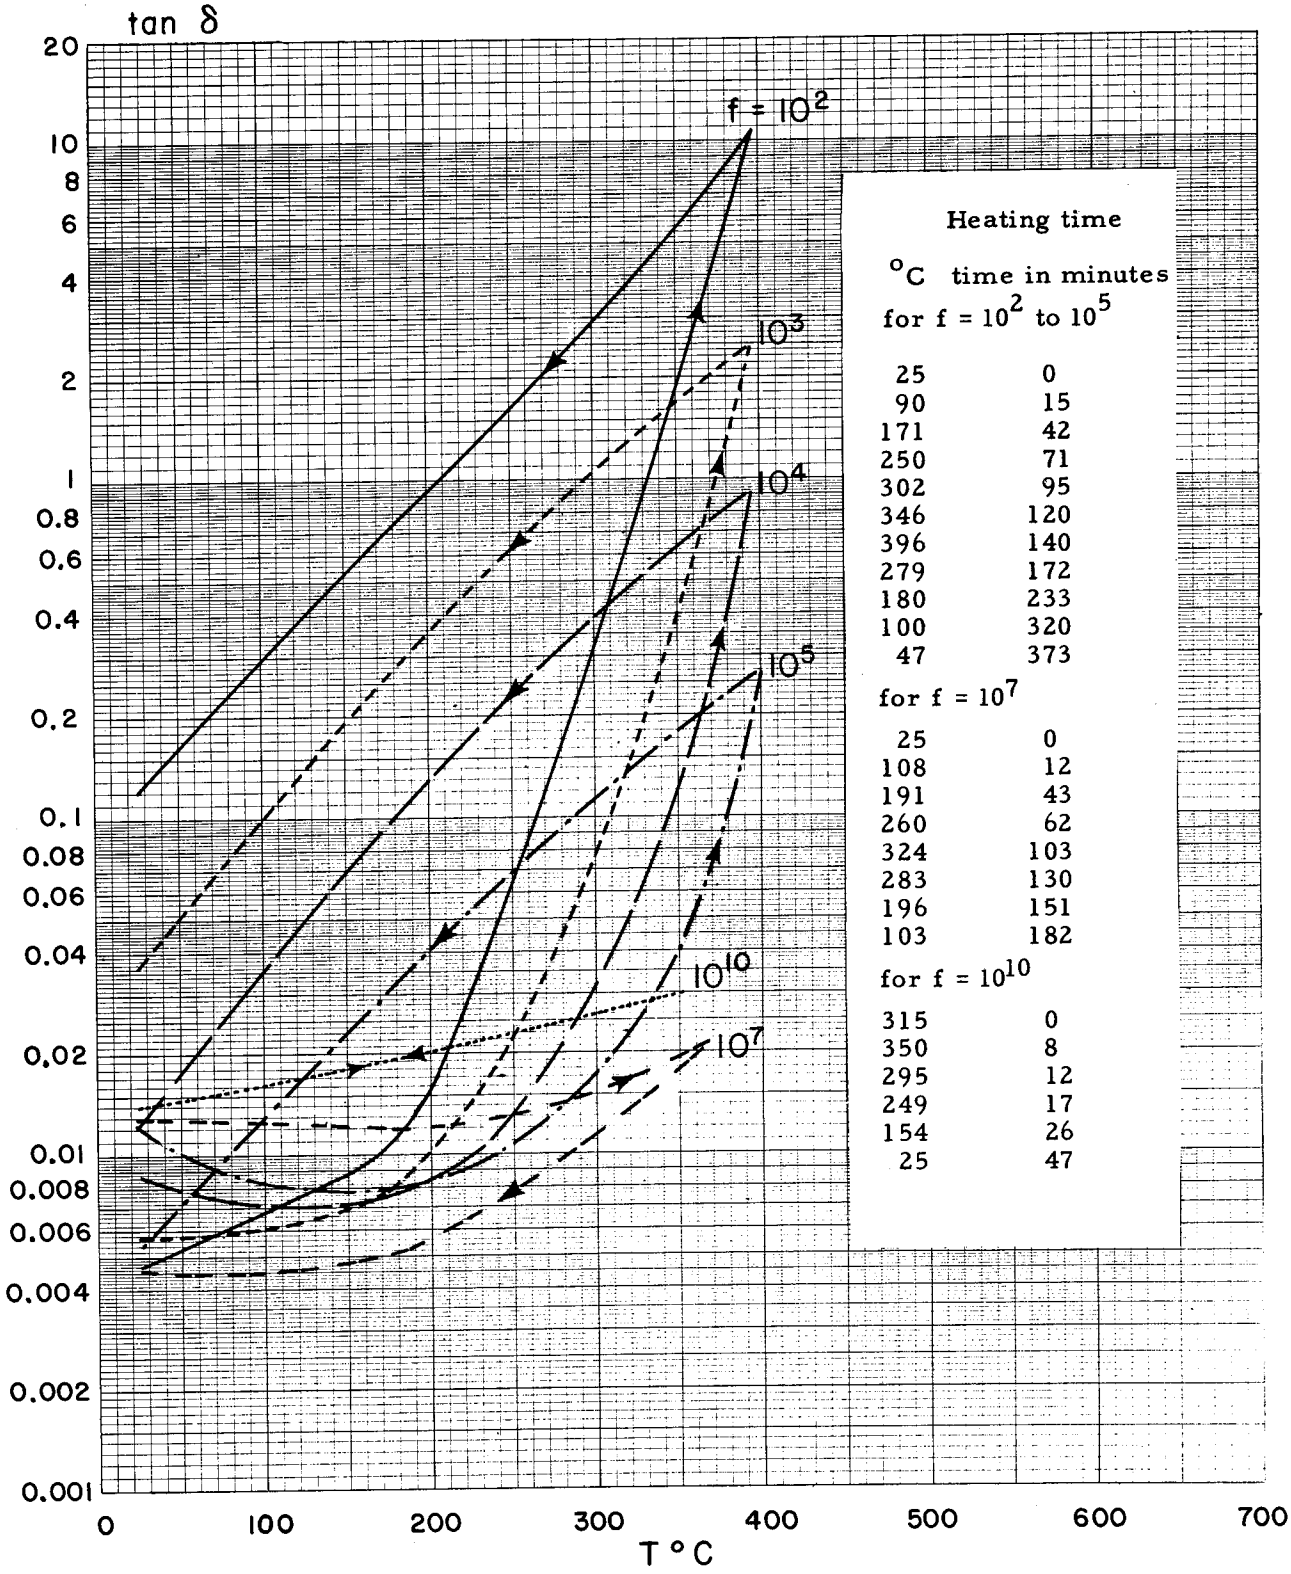


Heating time

°C	time in minutes
for f = 10^2 to 10^5	
25	0
90	15
171	42
250	71
302	95
346	120
396	140
279	172
180	233
100	320
47	373
for f = 10^7	
25	0
108	12
191	43
260	62
324	103
283	130
196	151
103	182
for f = 10^{10}	
315	0
350	8
295	12
249	17
154	26
25	47

III B 9. Polyesters


"Dilecto" GM-PE

Continental Diamond

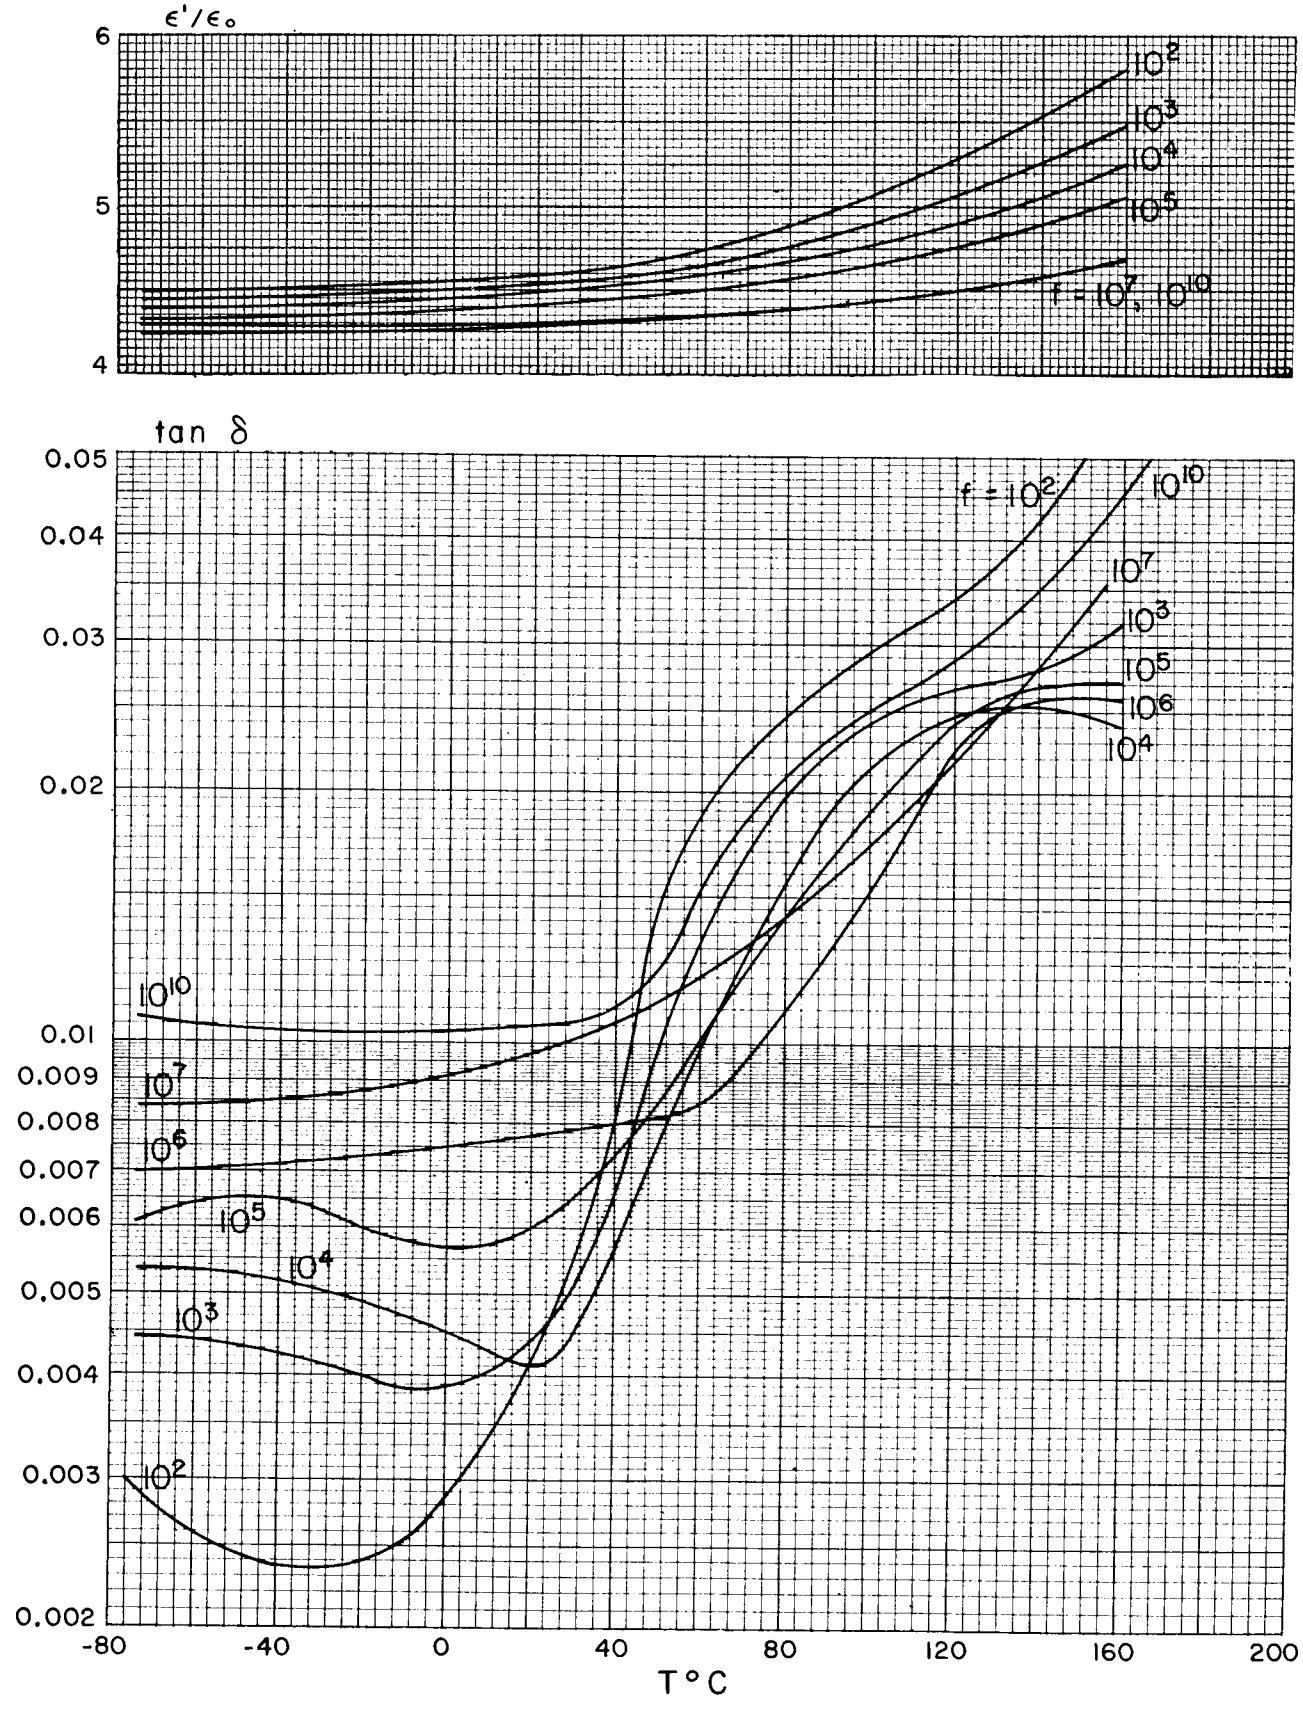

III B 9. Polyesters


"Cronar" du Pont photo products dept.

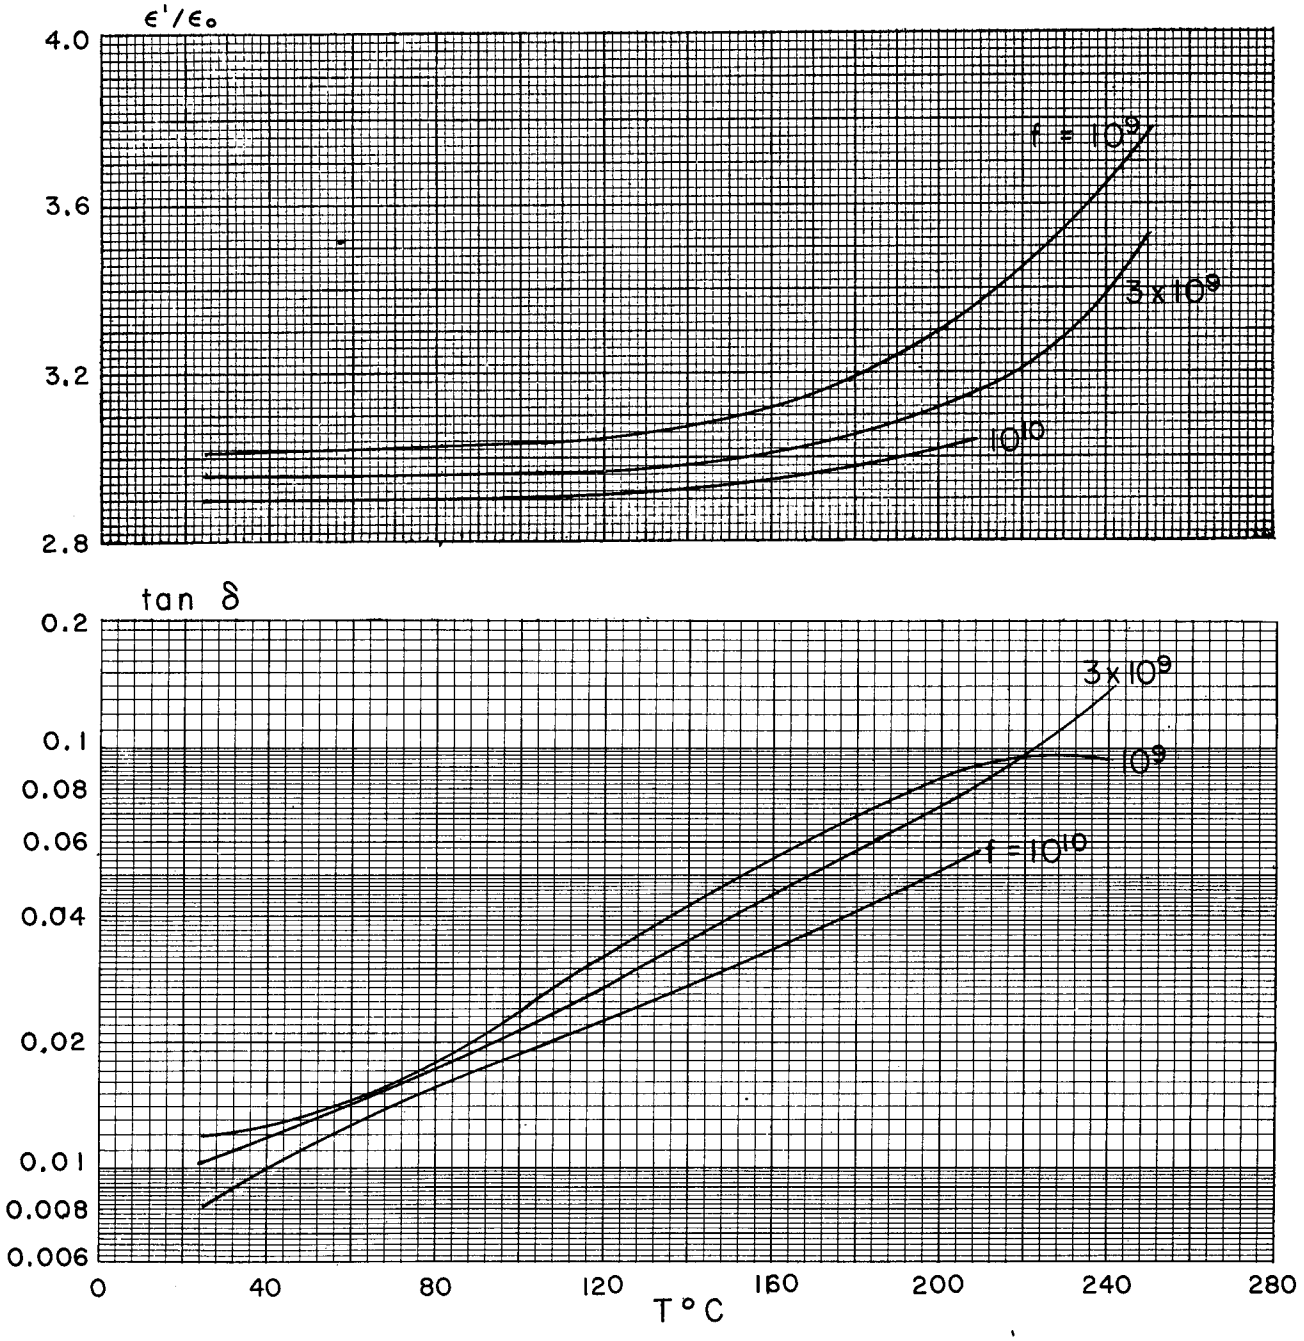

III B 9. Polyesters


"Dacron" Batt - "Stypol" 16B

du Pont

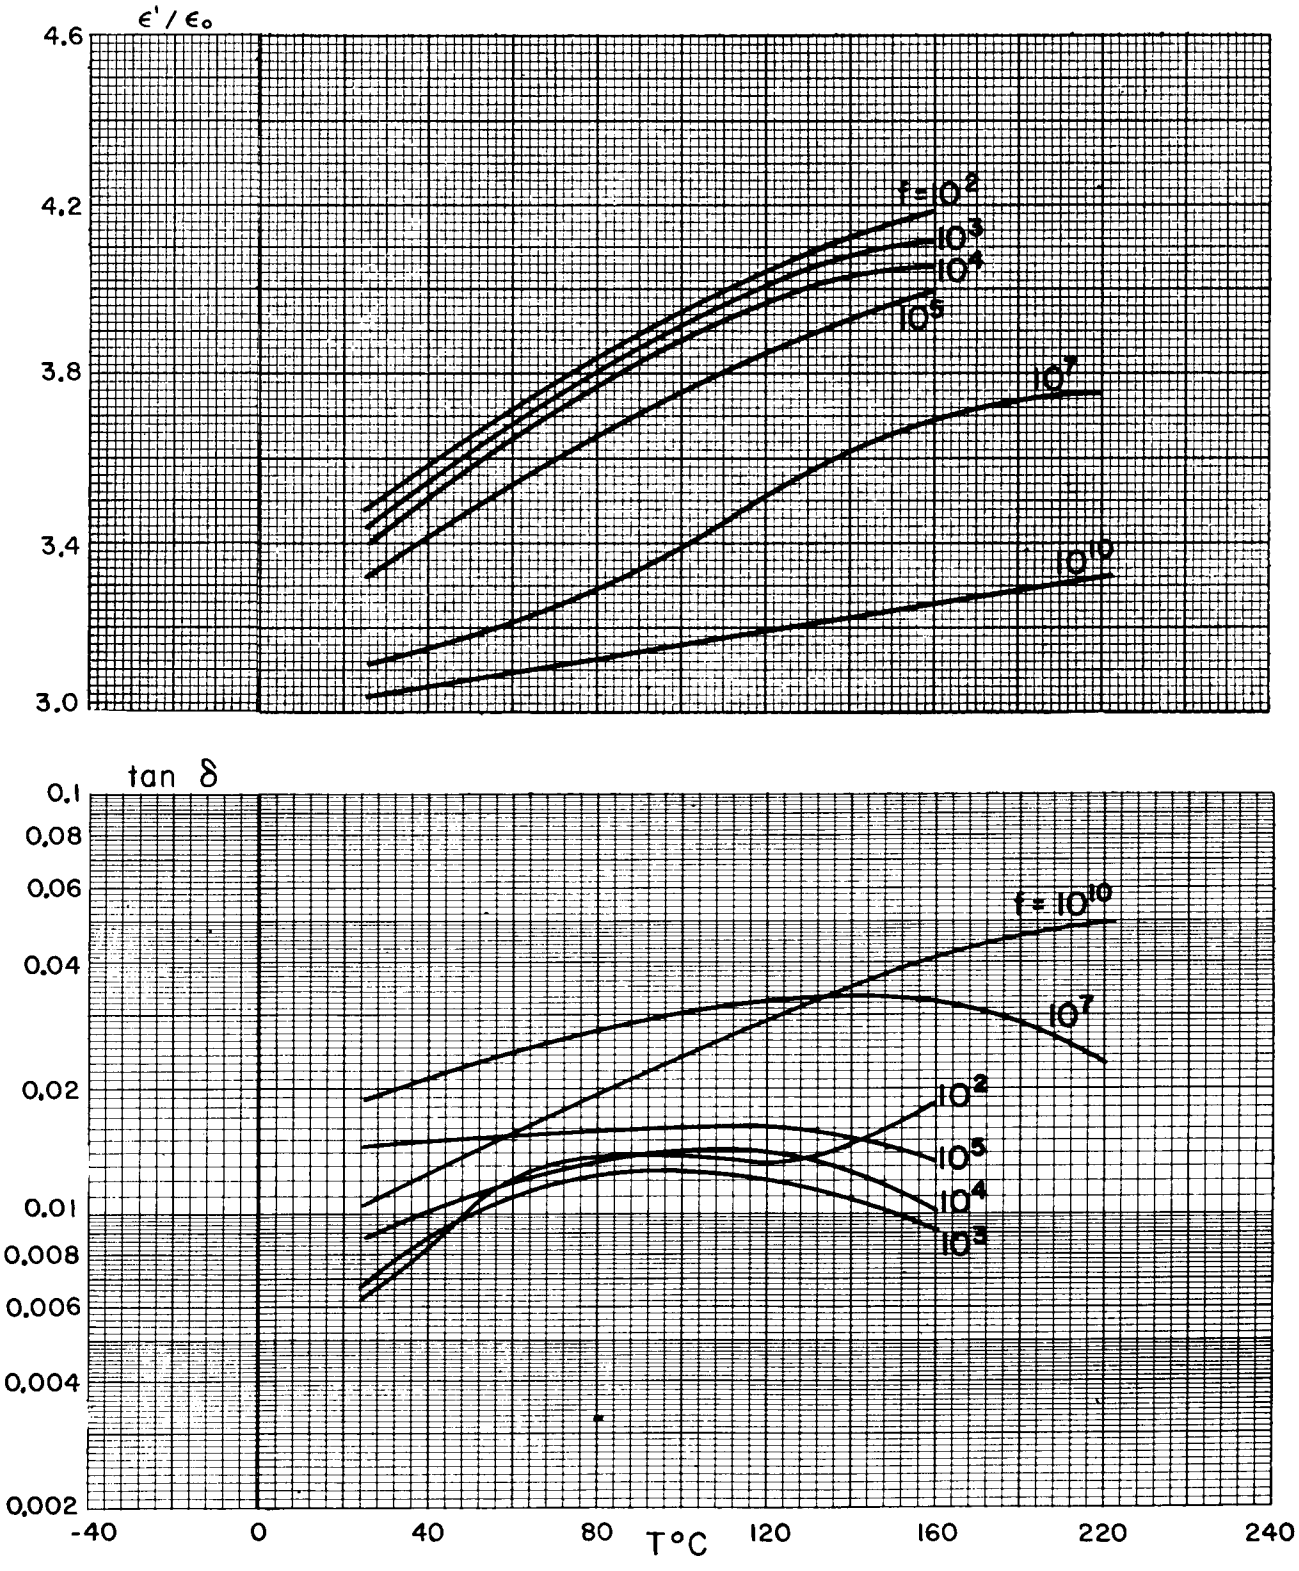

III B 9. Polyesters


"Paraplex"P43 Rohm and Haas

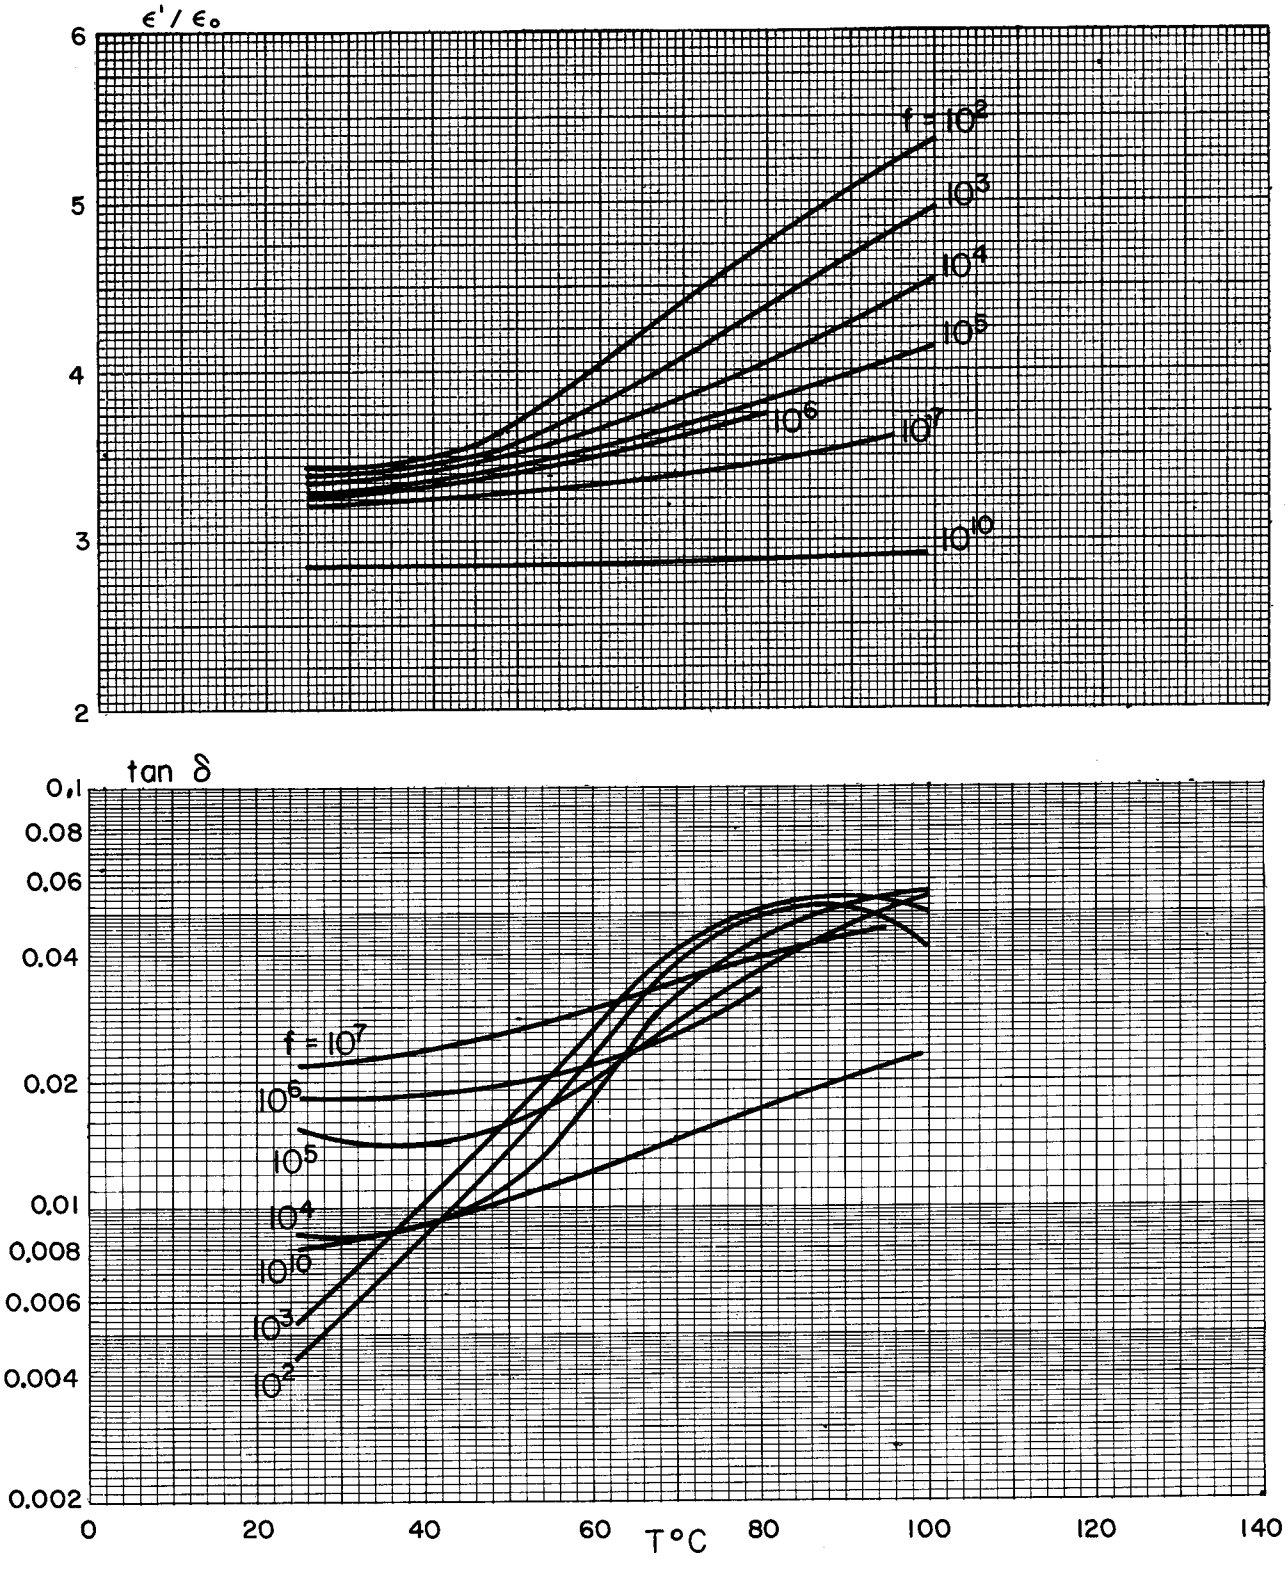

III B 10. Alkyd Resins

"Plaskon" Alkyd Special Electrical Granular


Plaskon Division
Allied Chemical and Dye Corp.

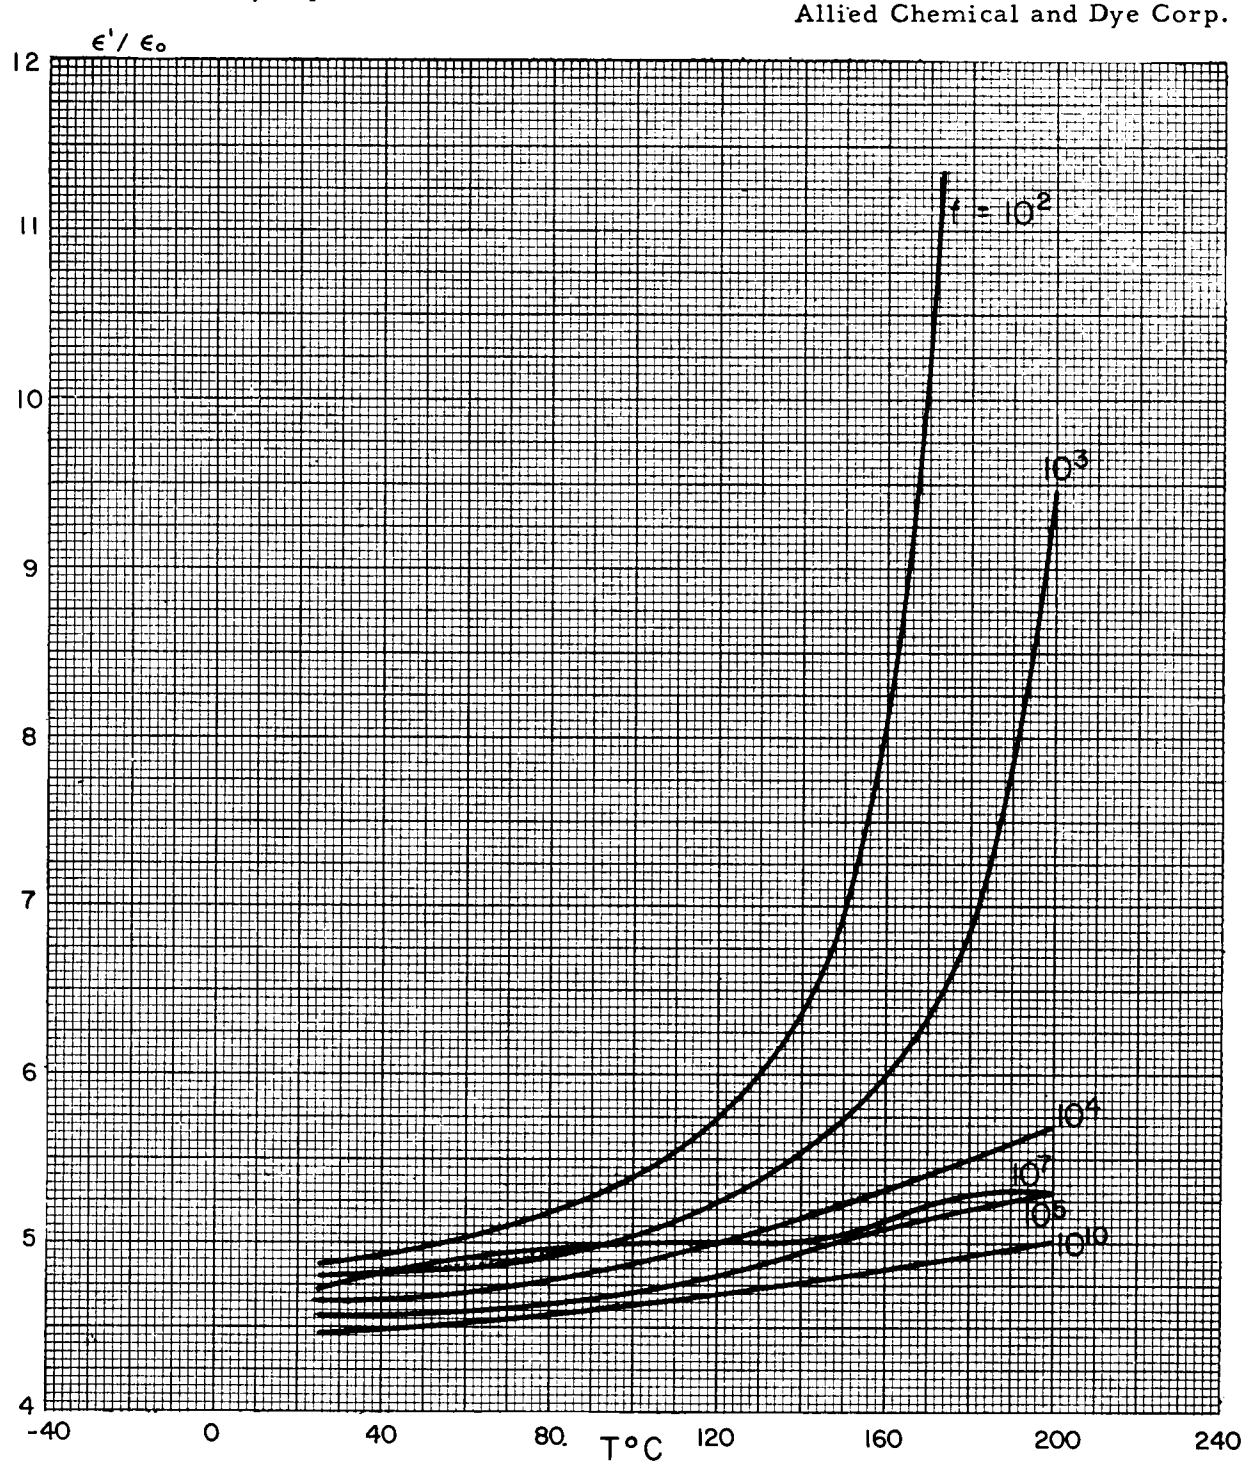

III B 10. Alkyd Resins


"Plaskon" Alkyd Special Electrical Granular

Plaskon Division
Allied Chemical and Dye Corp.

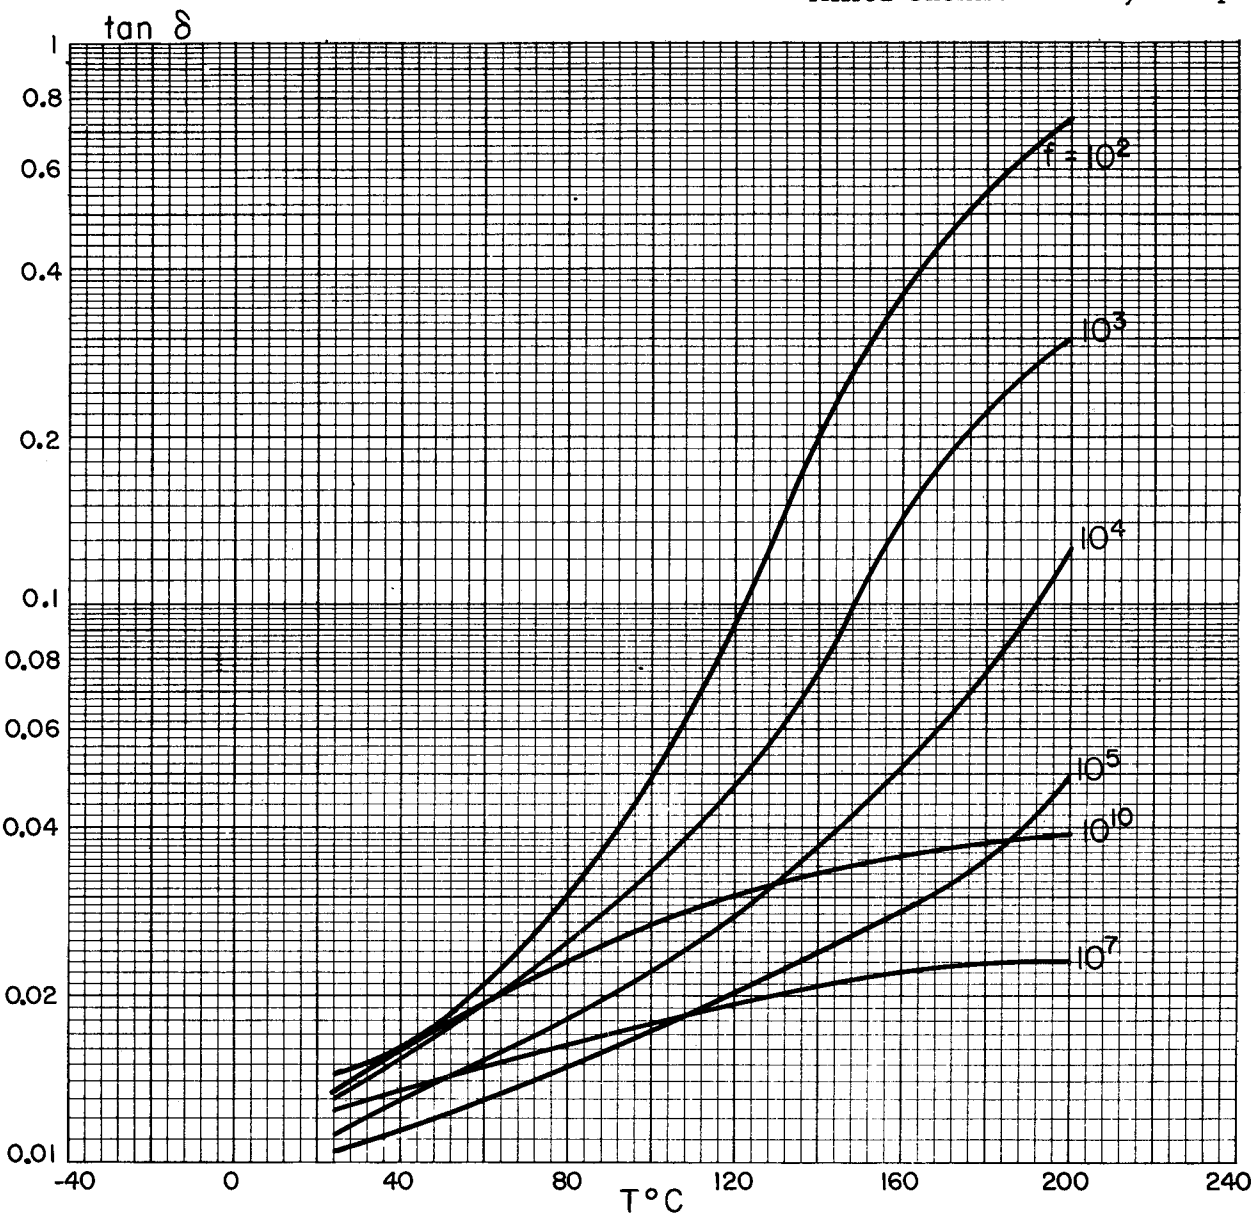

III B 11. Epoxy Resins


"Dilecto" (Epoxy-glass laminate) GB-181-E — Continental Diamond

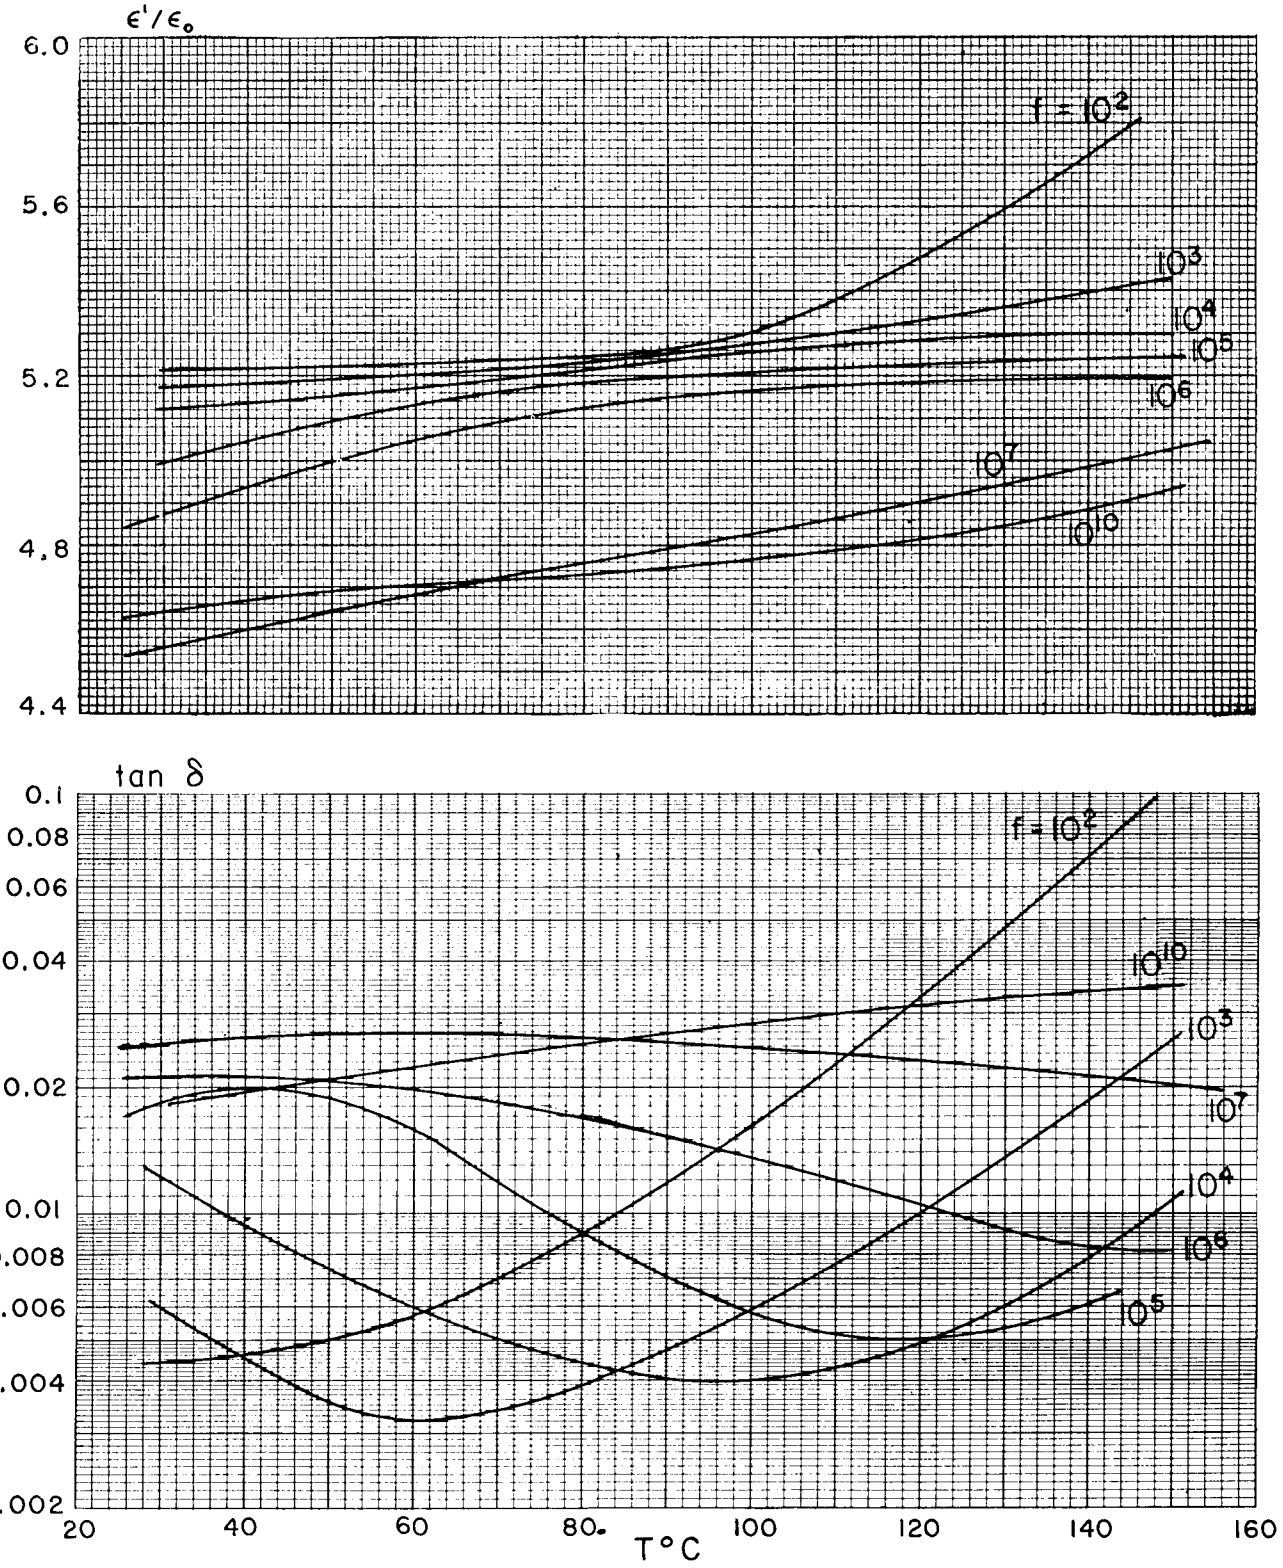

III B 11. Epoxy Resins


"Eccofoam" HiK (500°F)
(K=5.9, K=4.5, K=2.4)

Emerson and Cuming

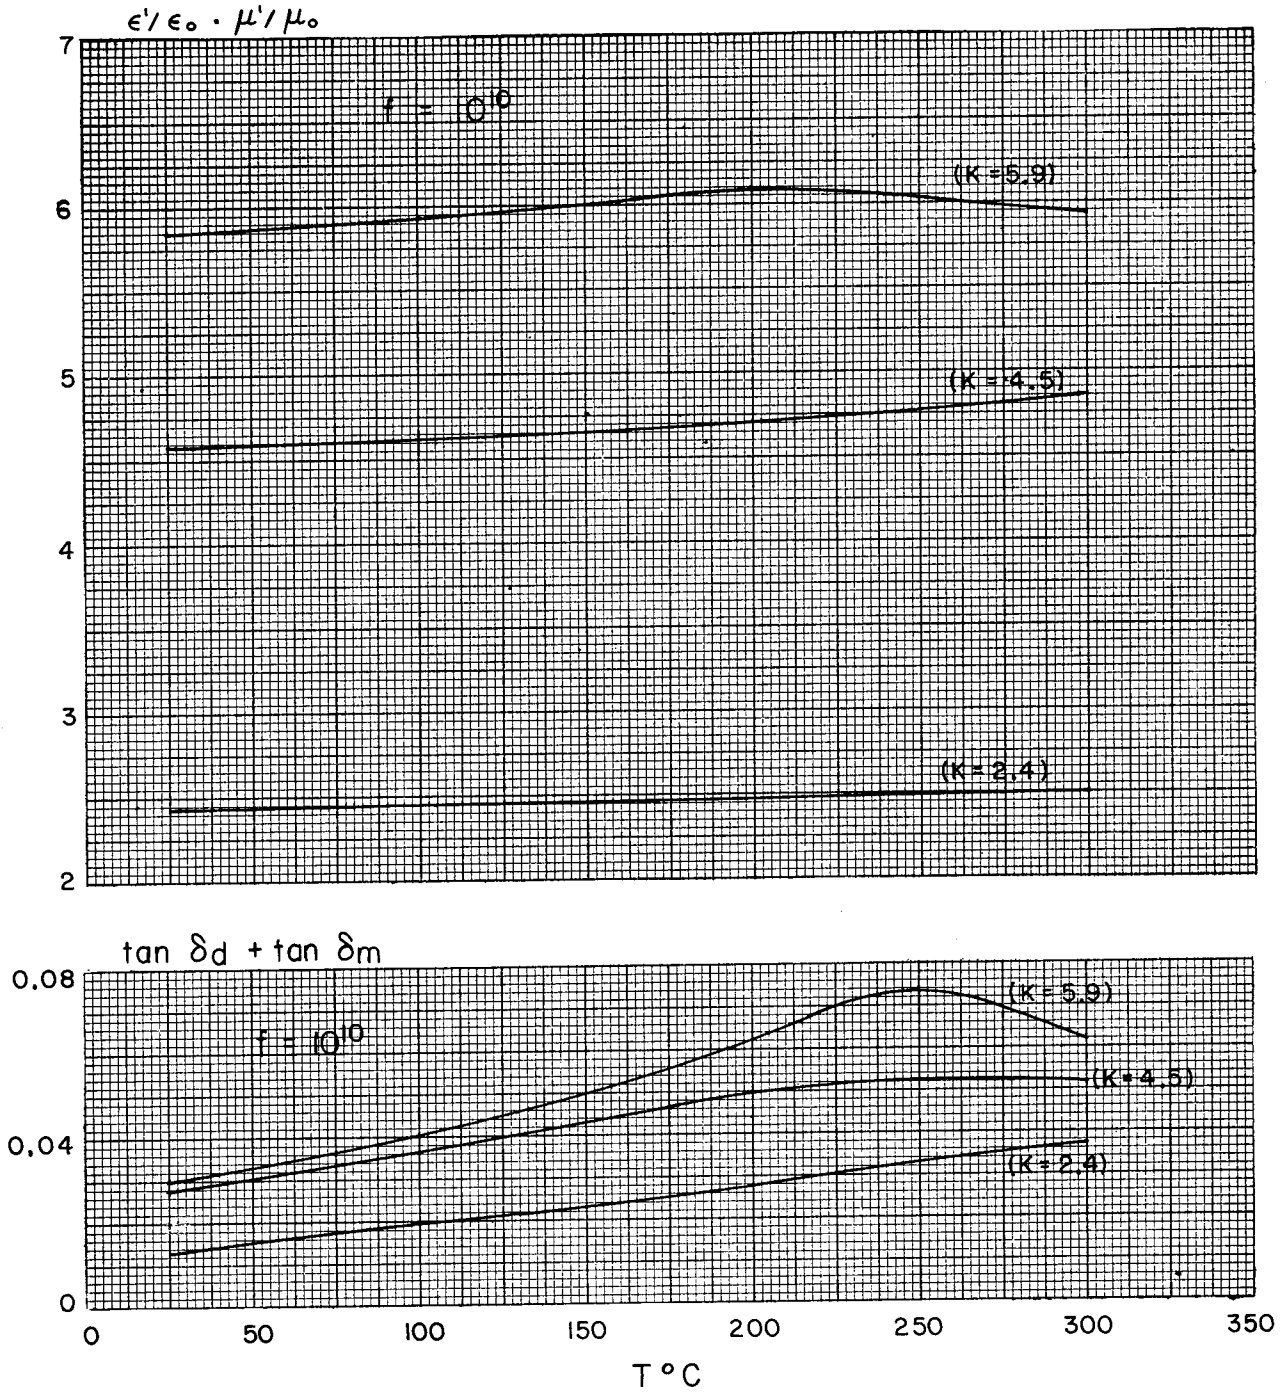


III B 11. Epoxy Resins

"Epon" 828 with curing agent CL — Shell Chemical

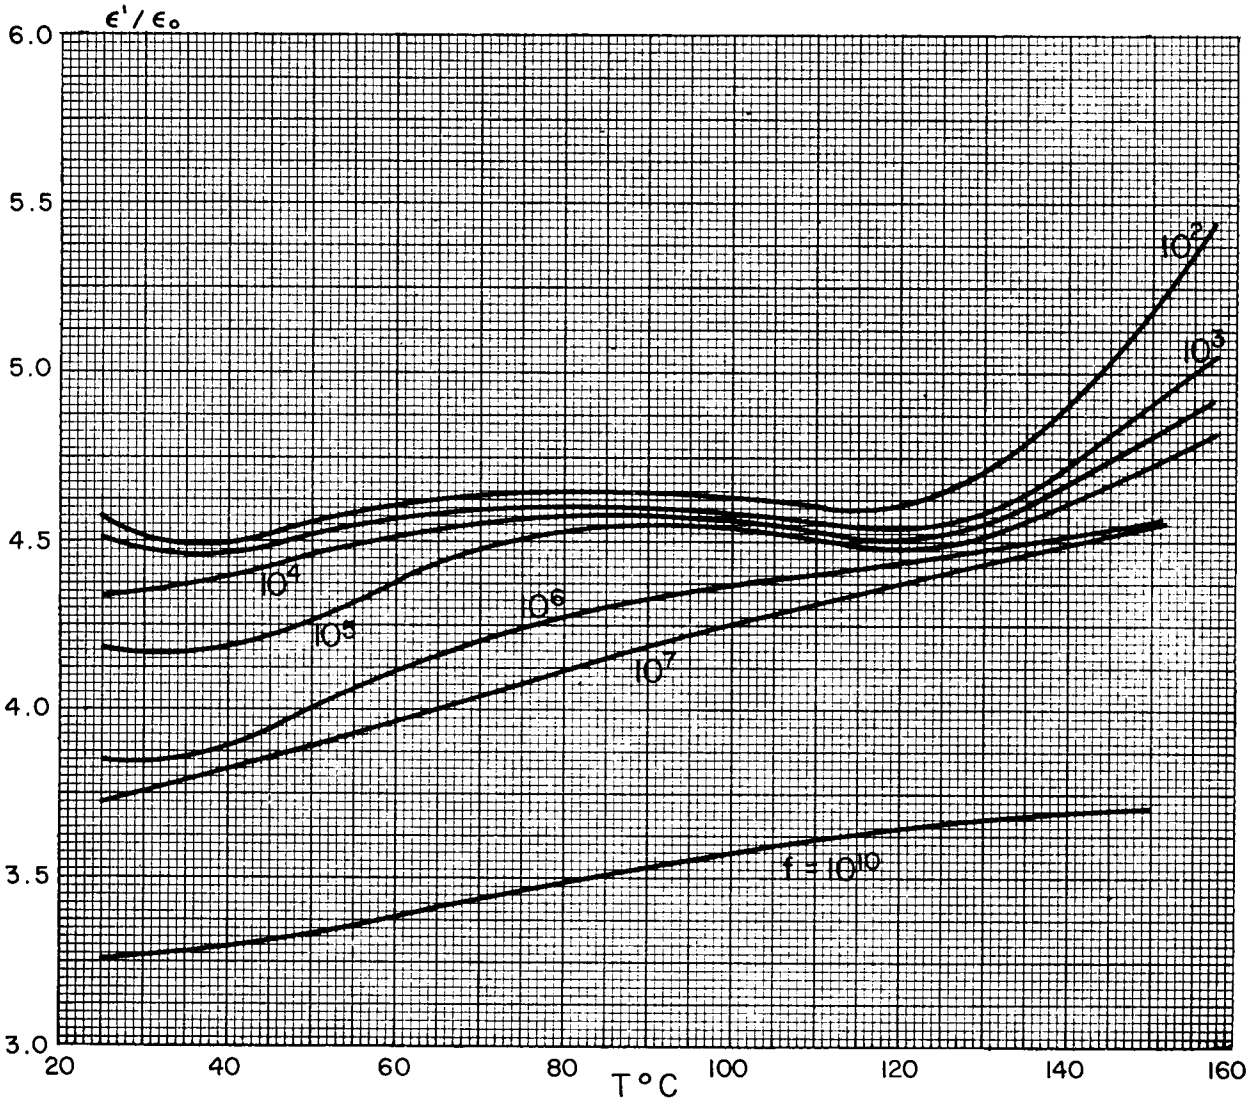


III B 11. Epoxy Resins

"Epon" 828 with curing agent CL — Shell Chemical

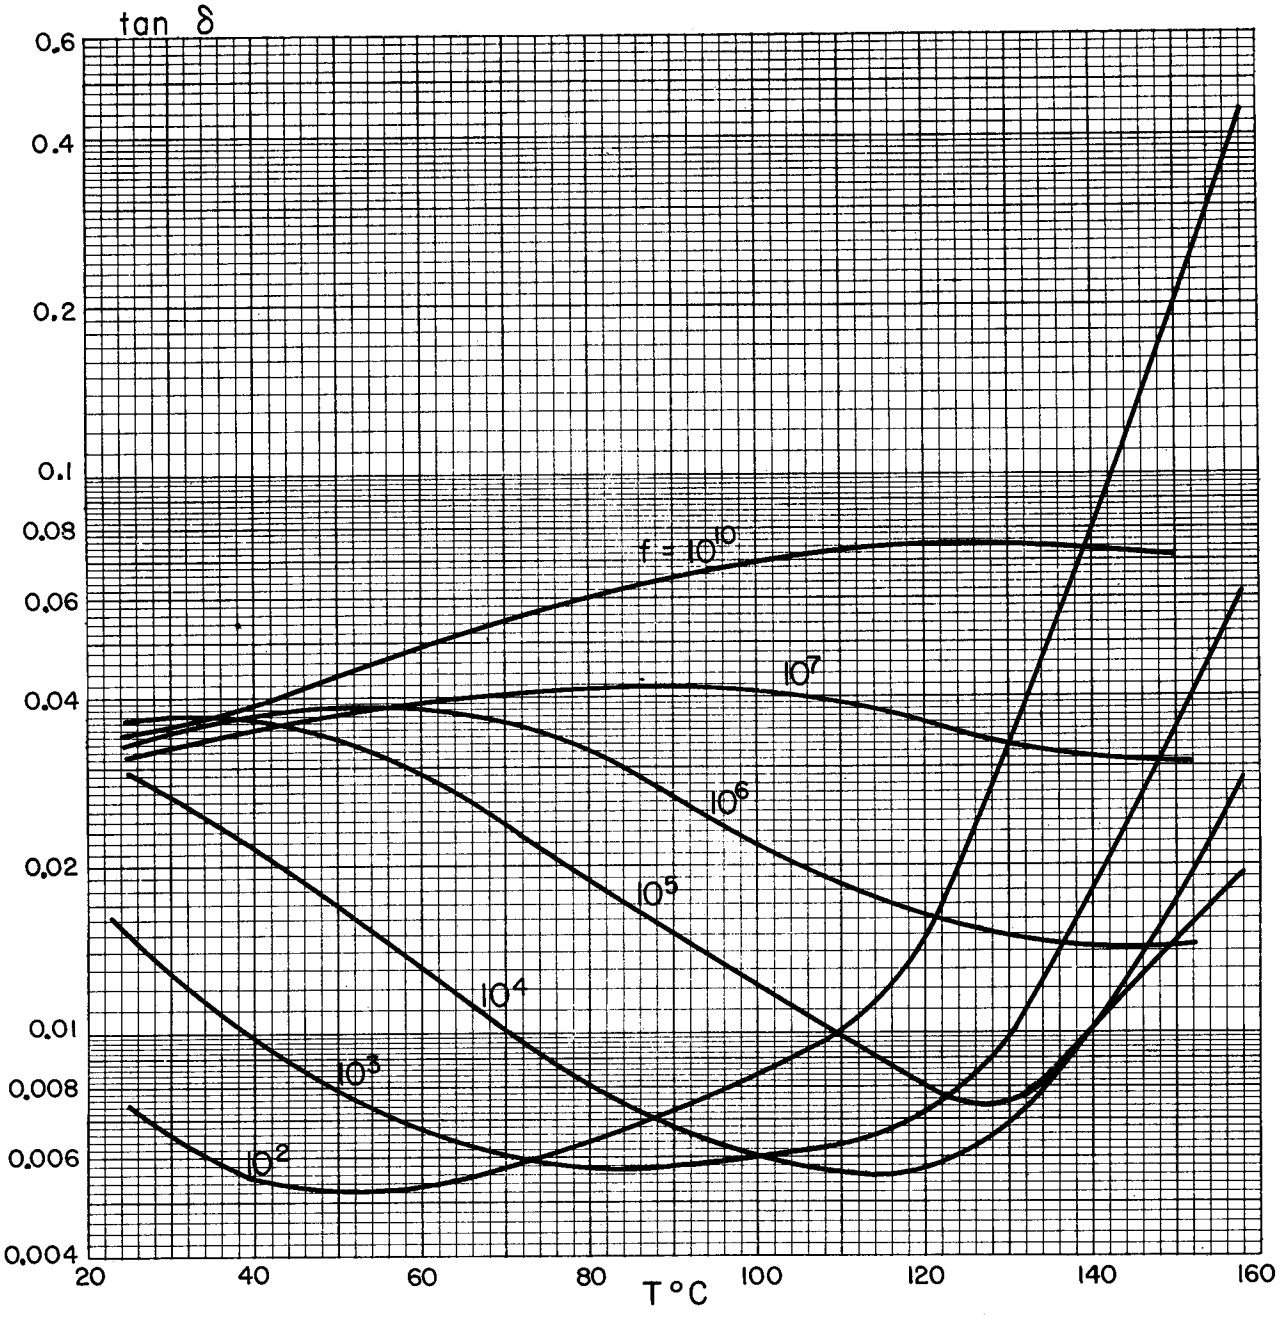

III B 11. Epoxy Resins


"Epon" 828 with curing agent D — Shell Chemical

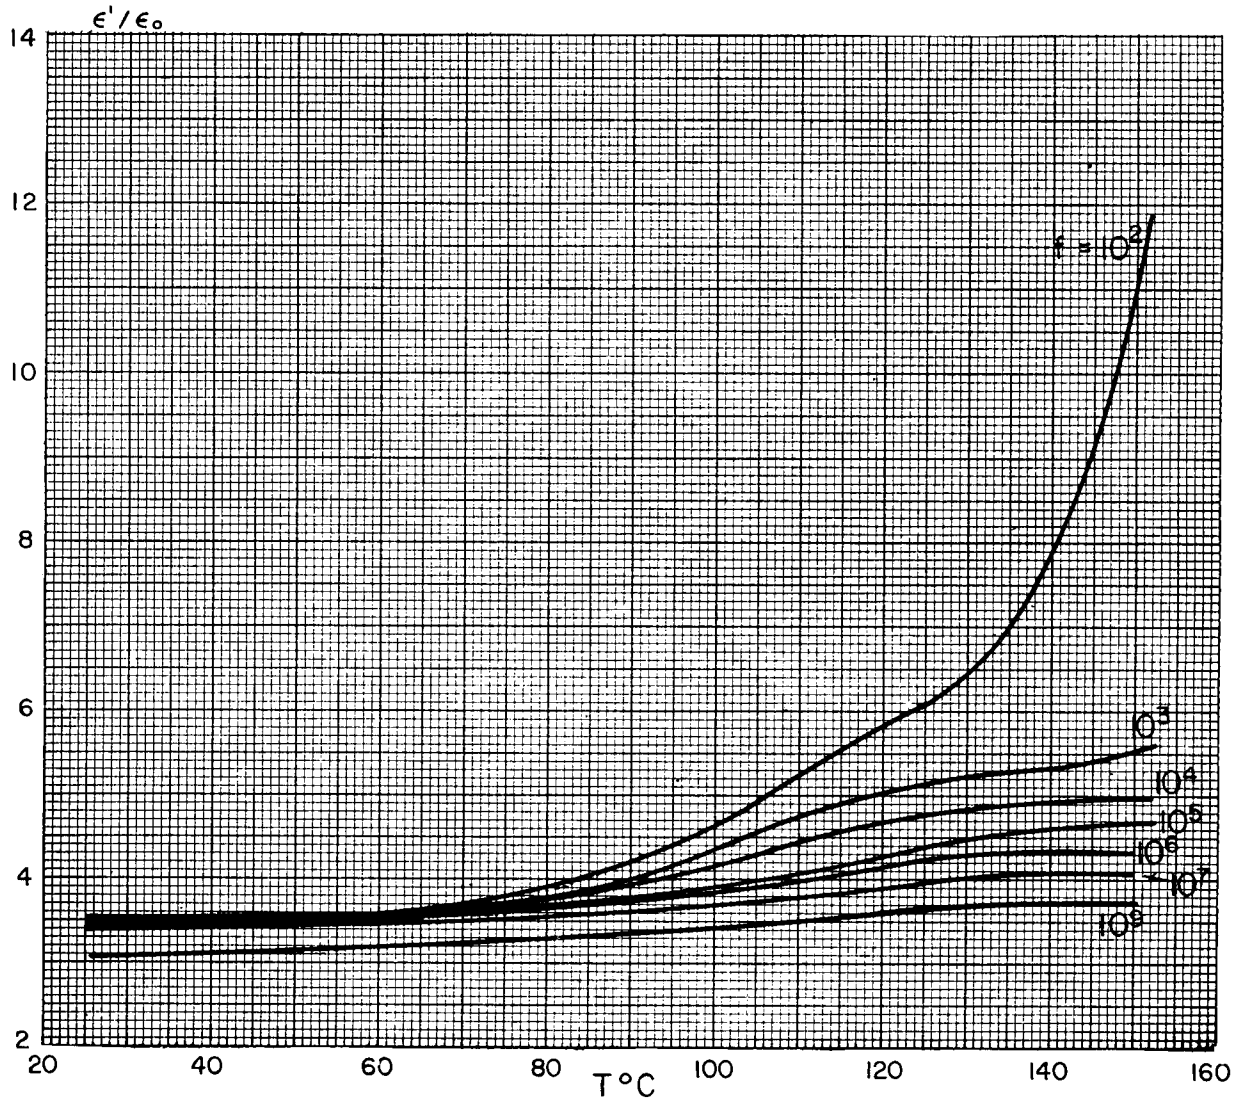

III B 11. Epoxy Resins


"Epon" 828 with curing agent D

Shell Chemical

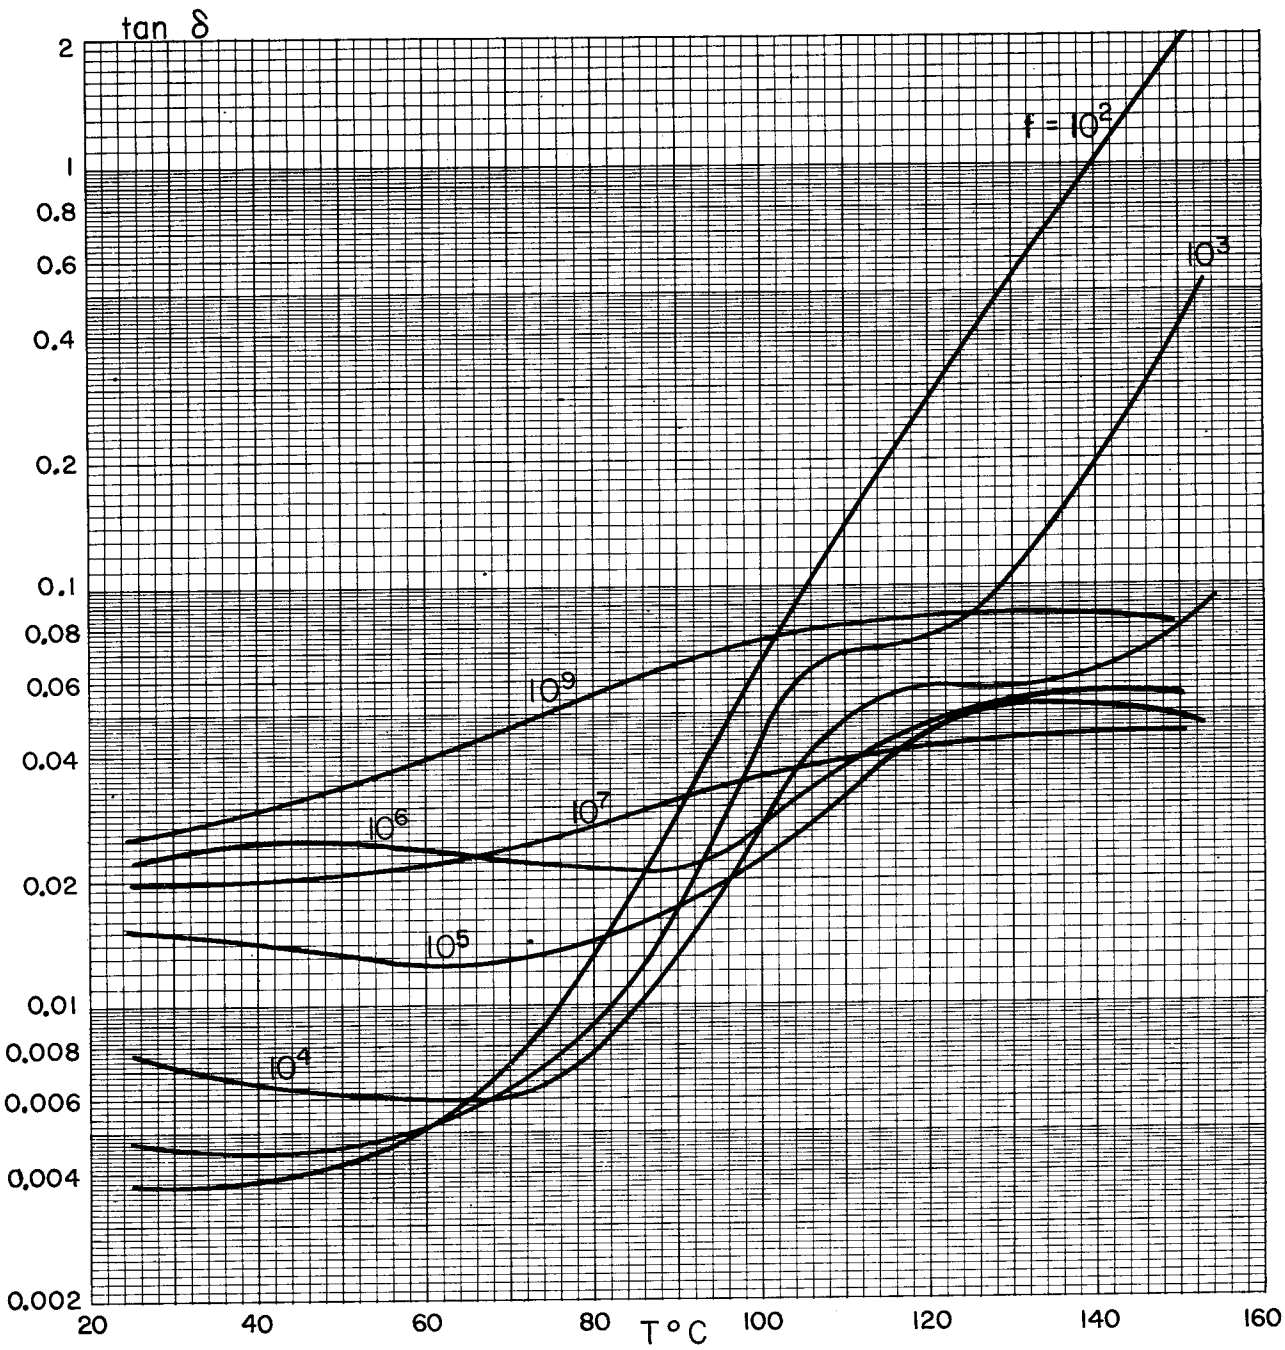


III B 11. Epoxy Resins

"Epon" 828 with "Piperidine" curing agent — Shell Chemical

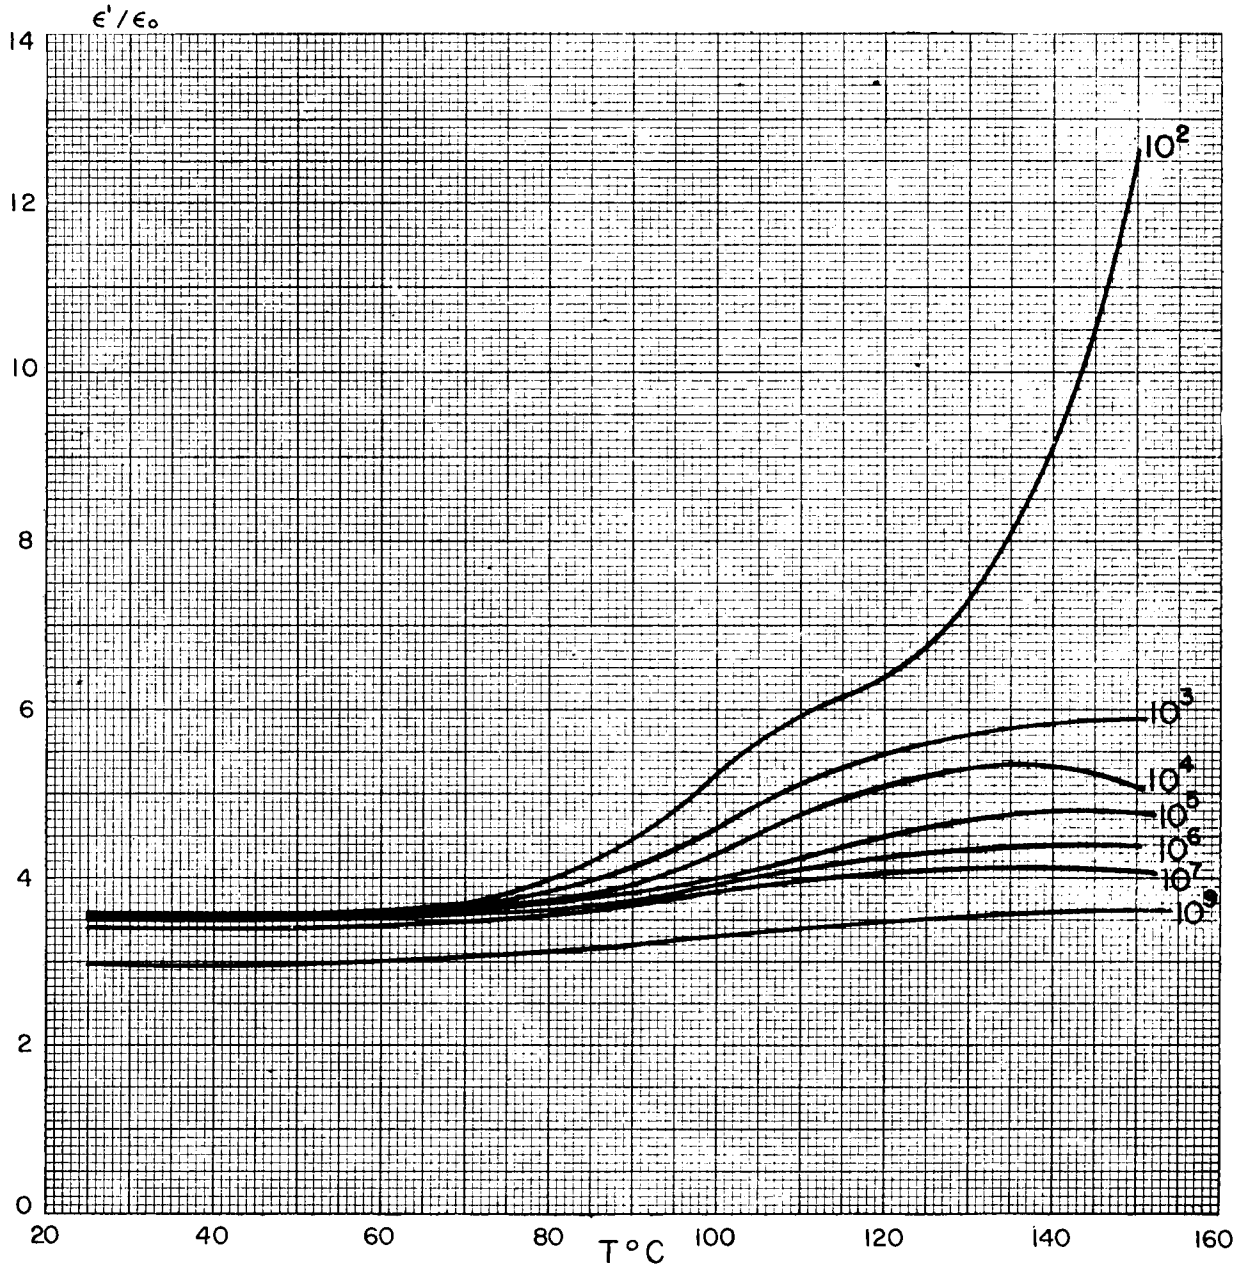


"Epon" 828 with "Piperidine" curing agent

Shell Chemical

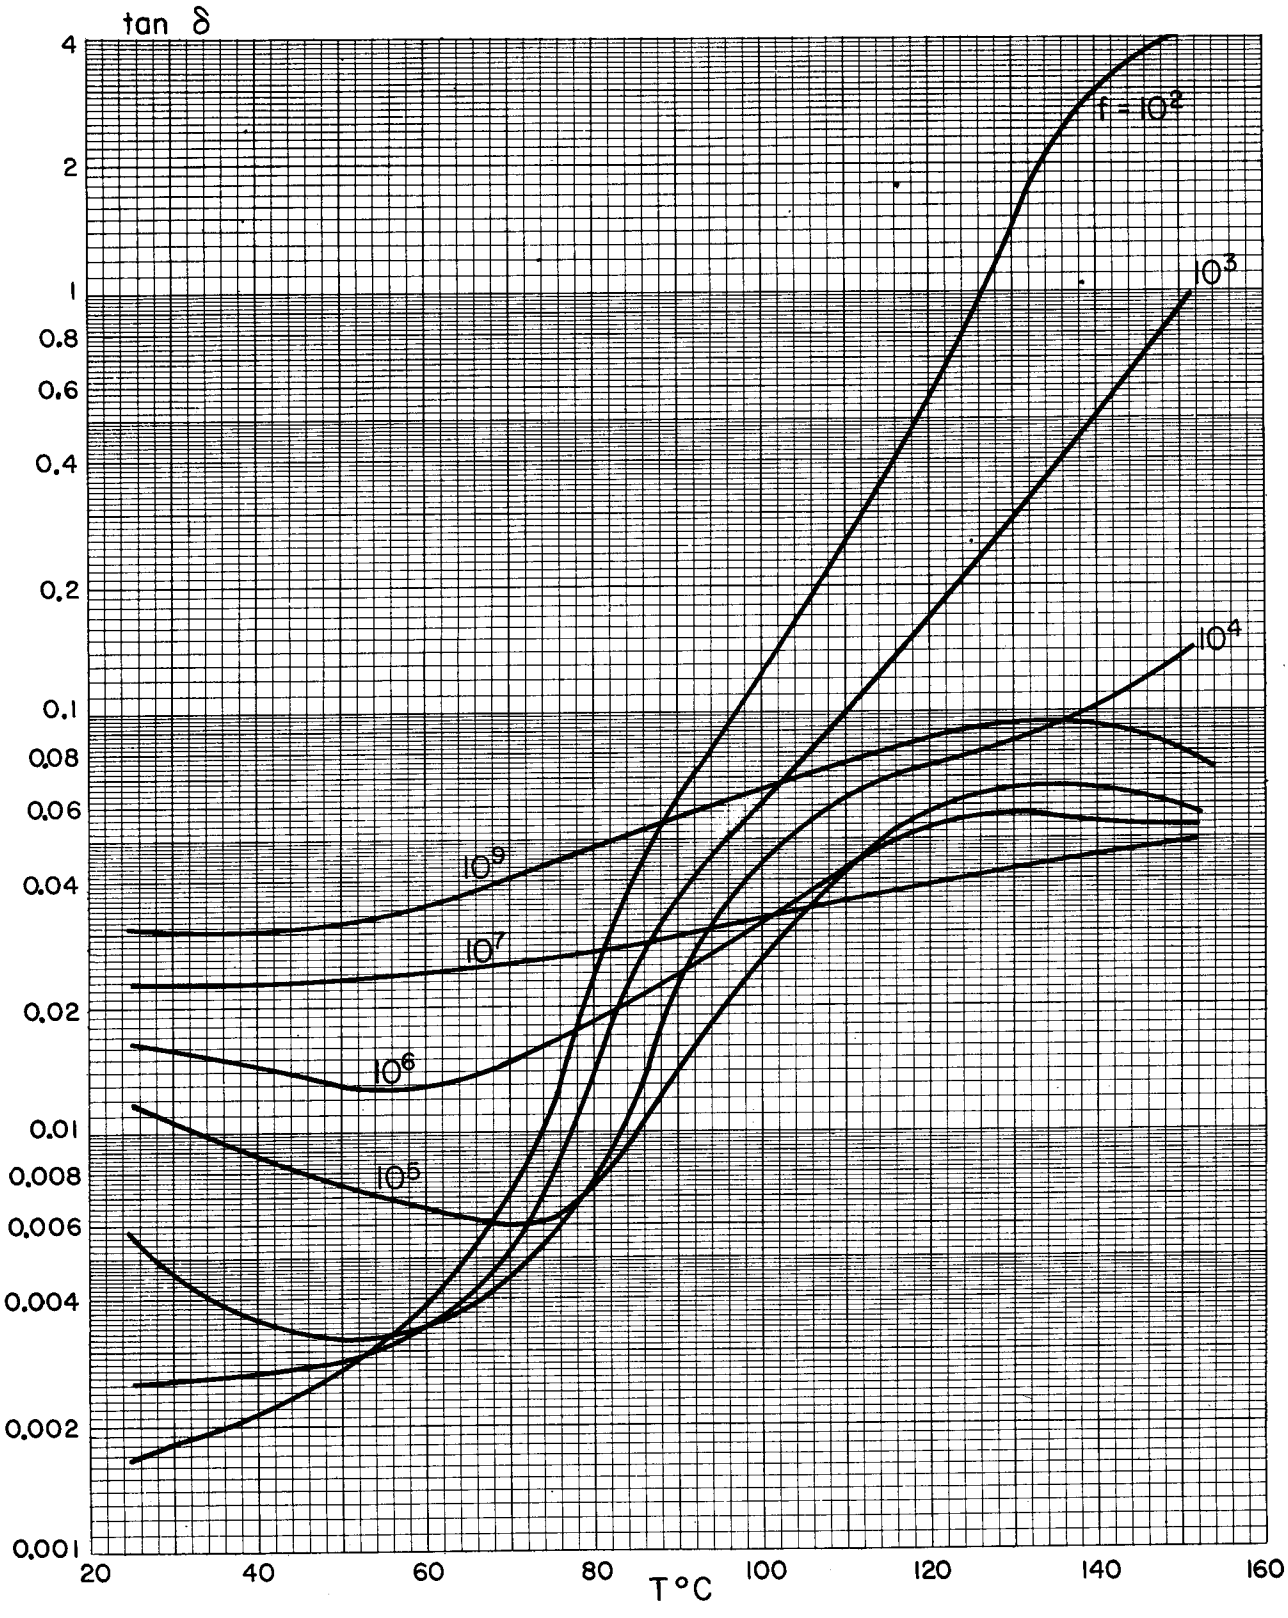


III B 11. Epoxy Resins

"Epon" 828 with curing agent BF_3-400 Shell Chemical

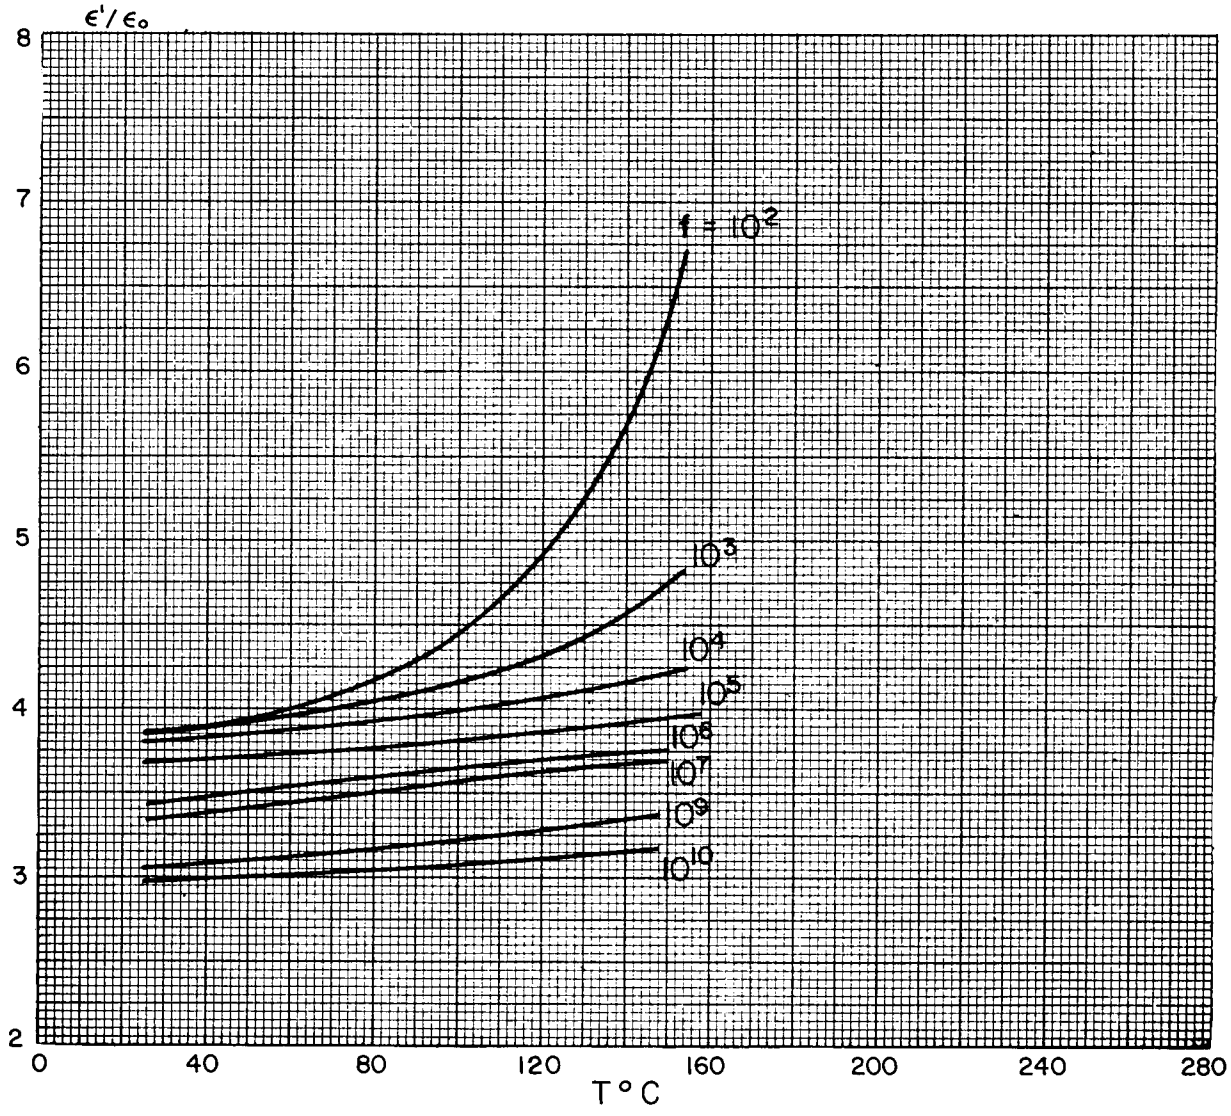

III B 11. Epoxy Resins


"Epon" 828 with curing agent BF_3-400 — Shell Chemical

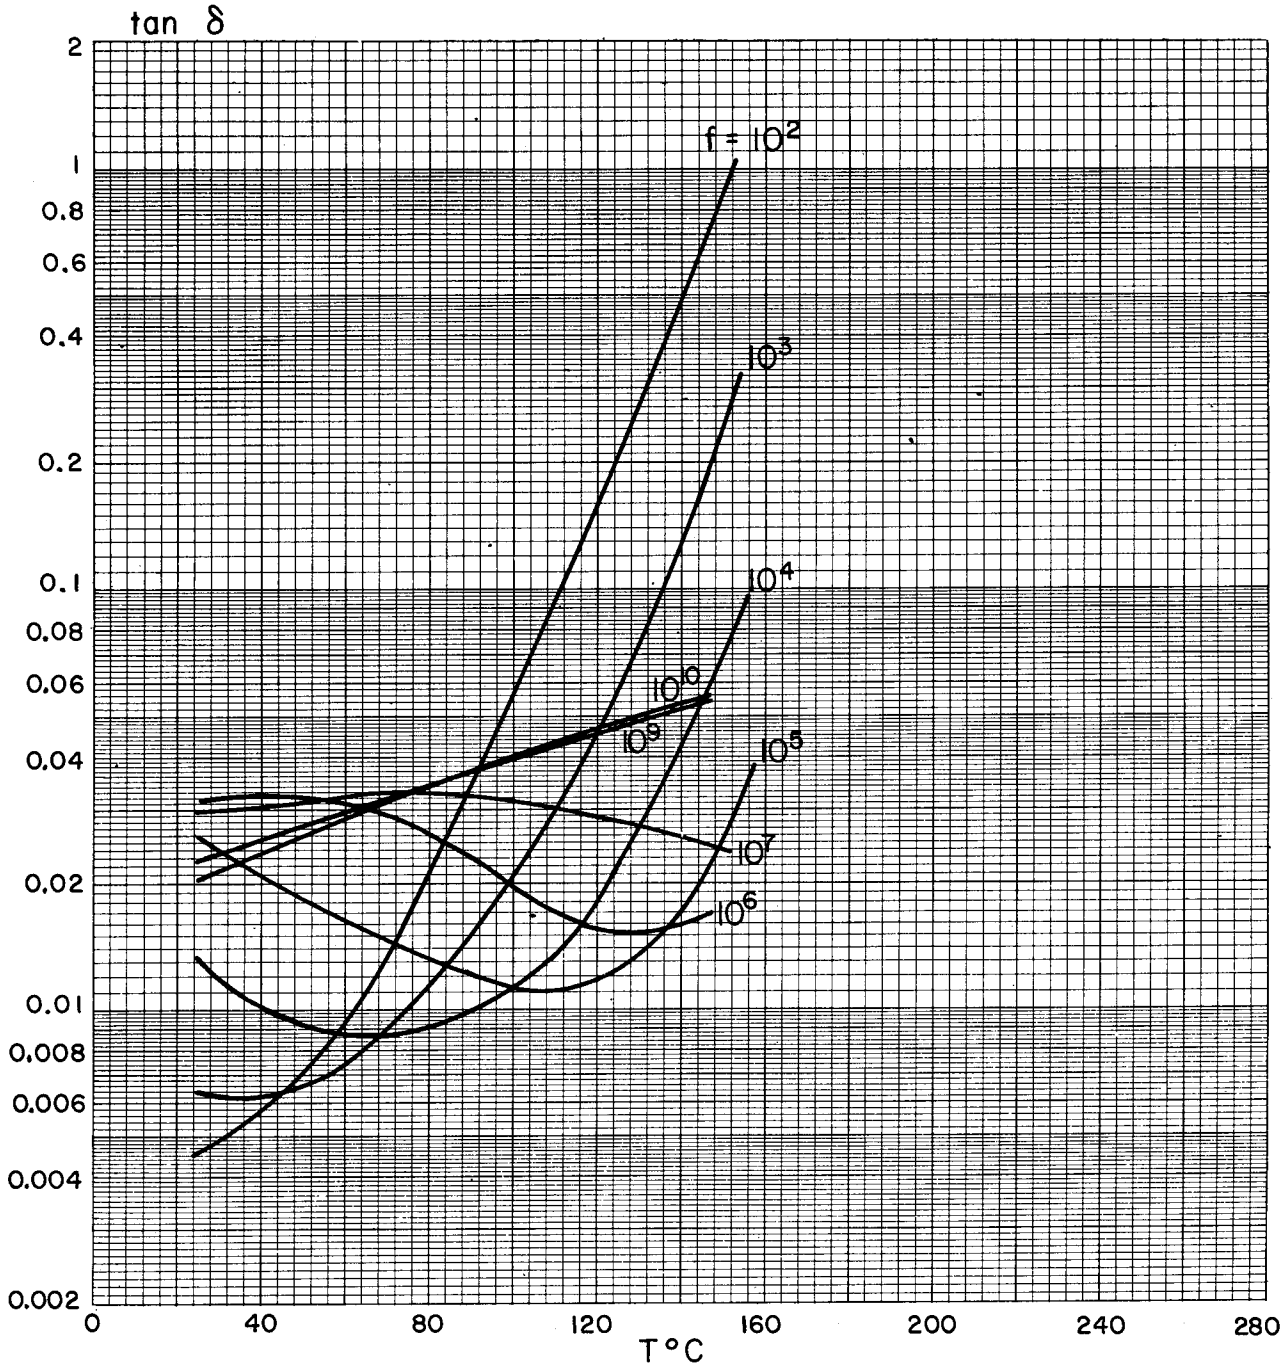

III B 11. Epoxy Resins

"Epon" 828 "fiberglas" laminate
(curing agent BF_3-400)


Shell Chemical

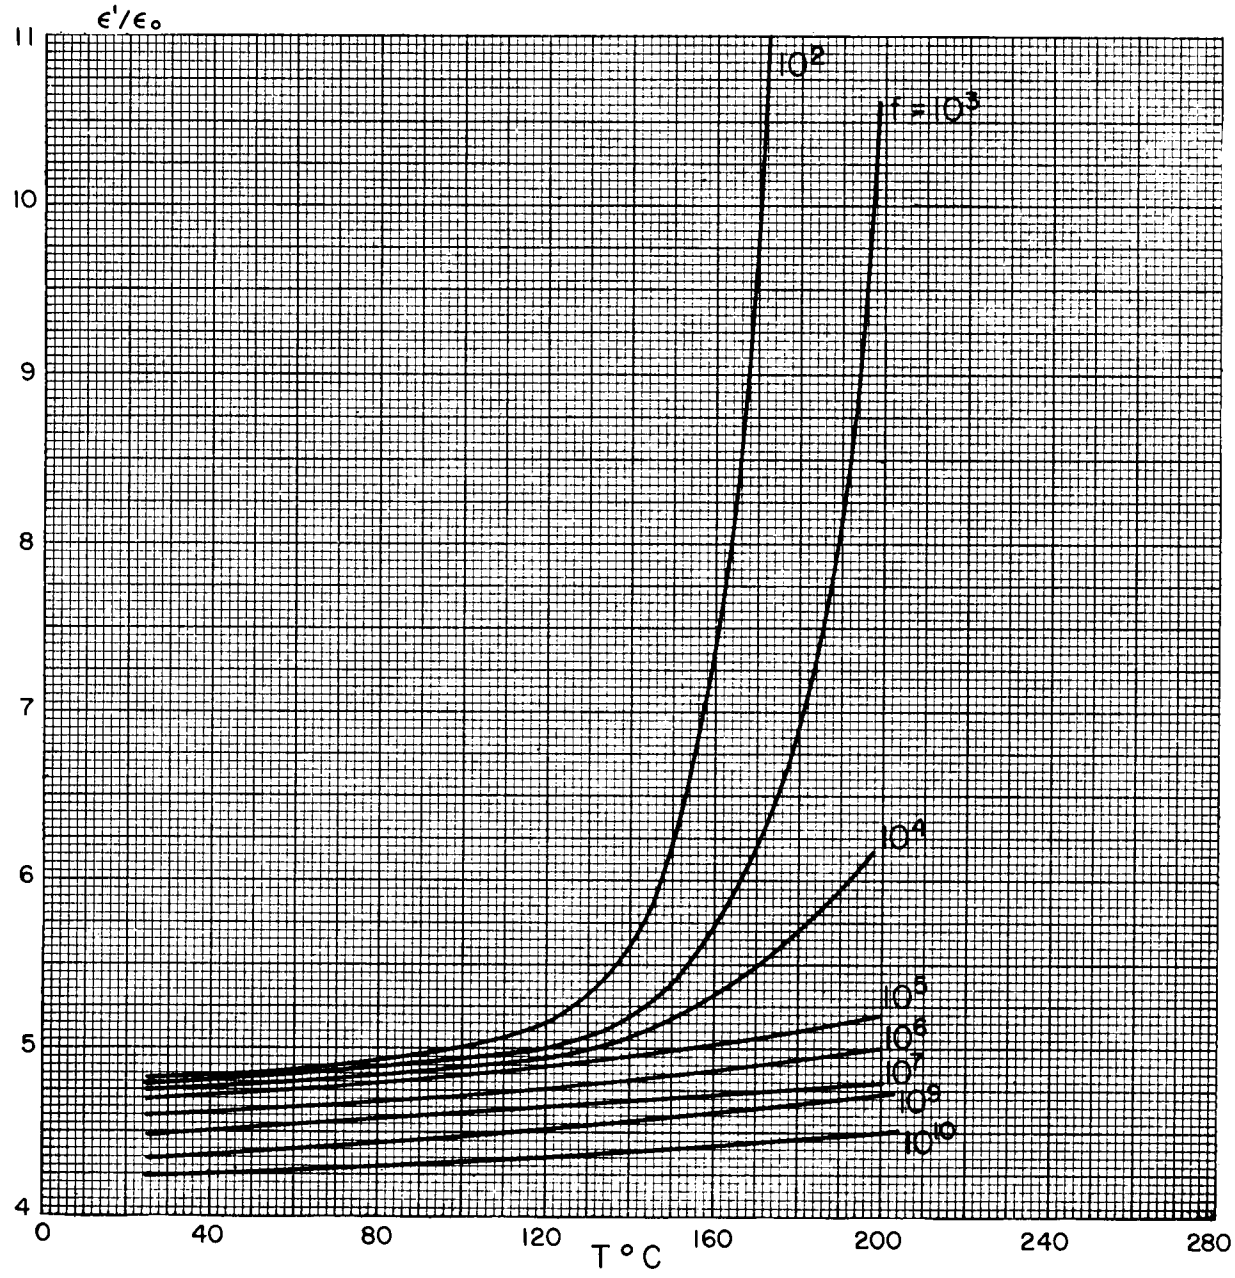

III B 11. Epoxy Resins

"Epon" 828 "fiberglas" laminate
(curing agent BF_3-400)


Shell Chemical

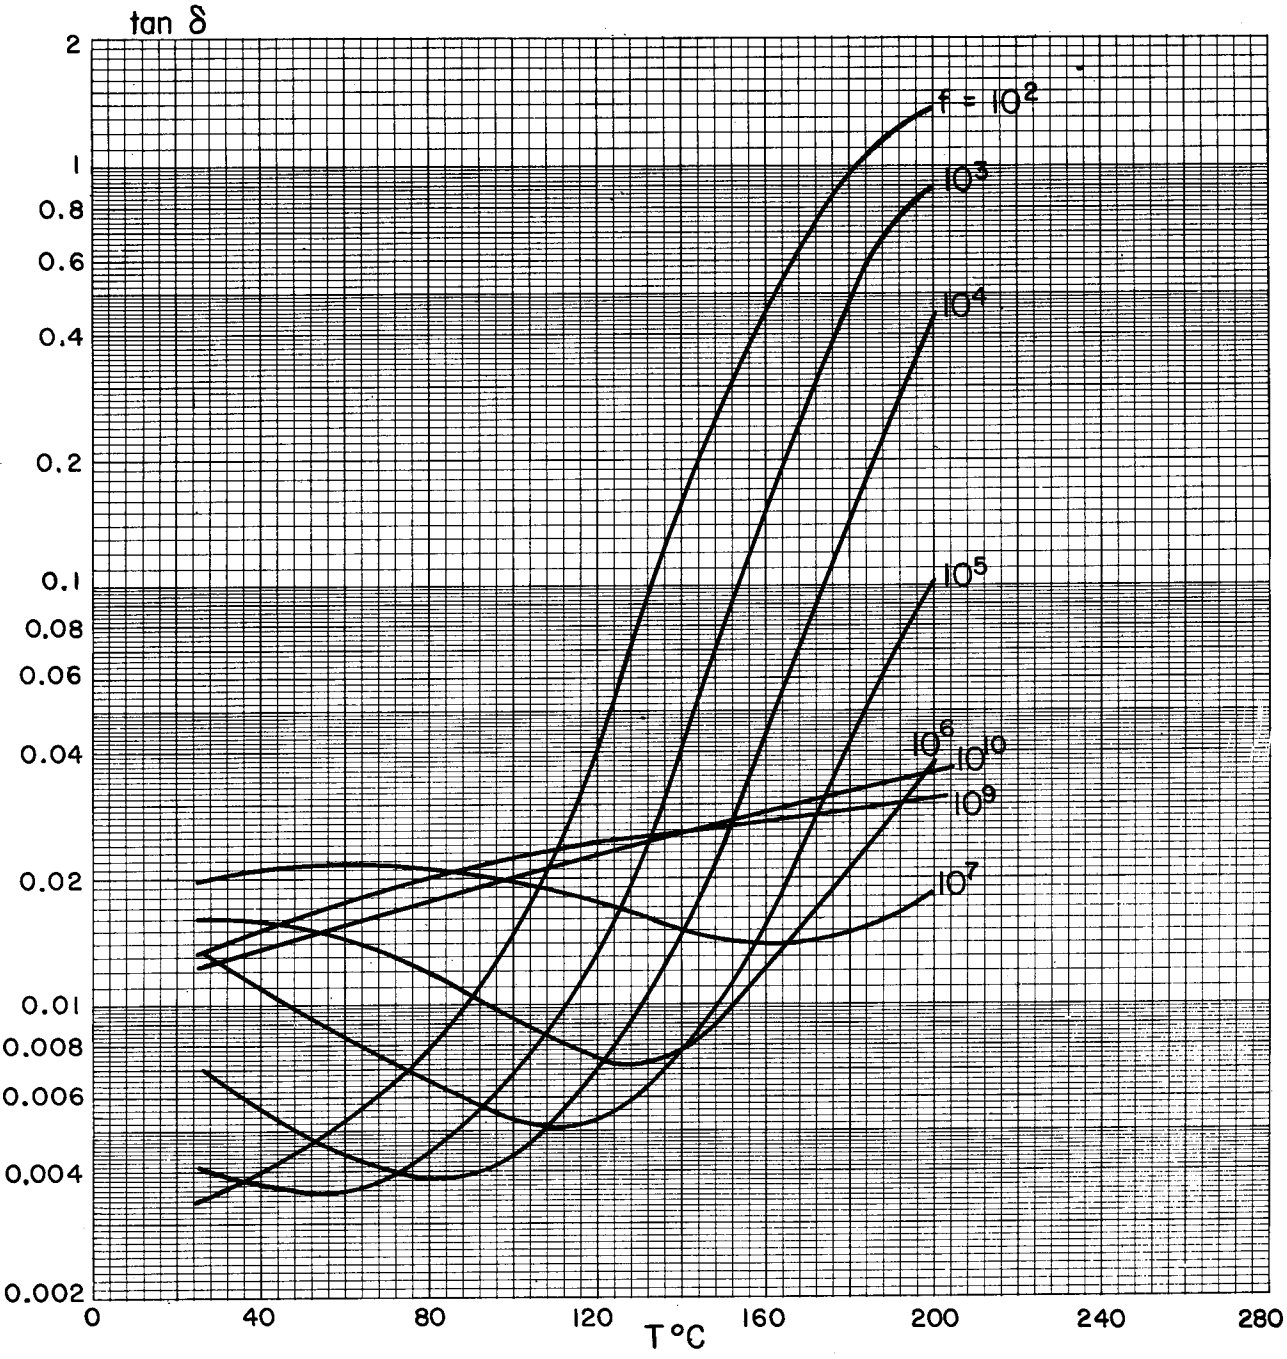

III B 11. Epoxy Resins


"Hysol" 6000HD

Houghton

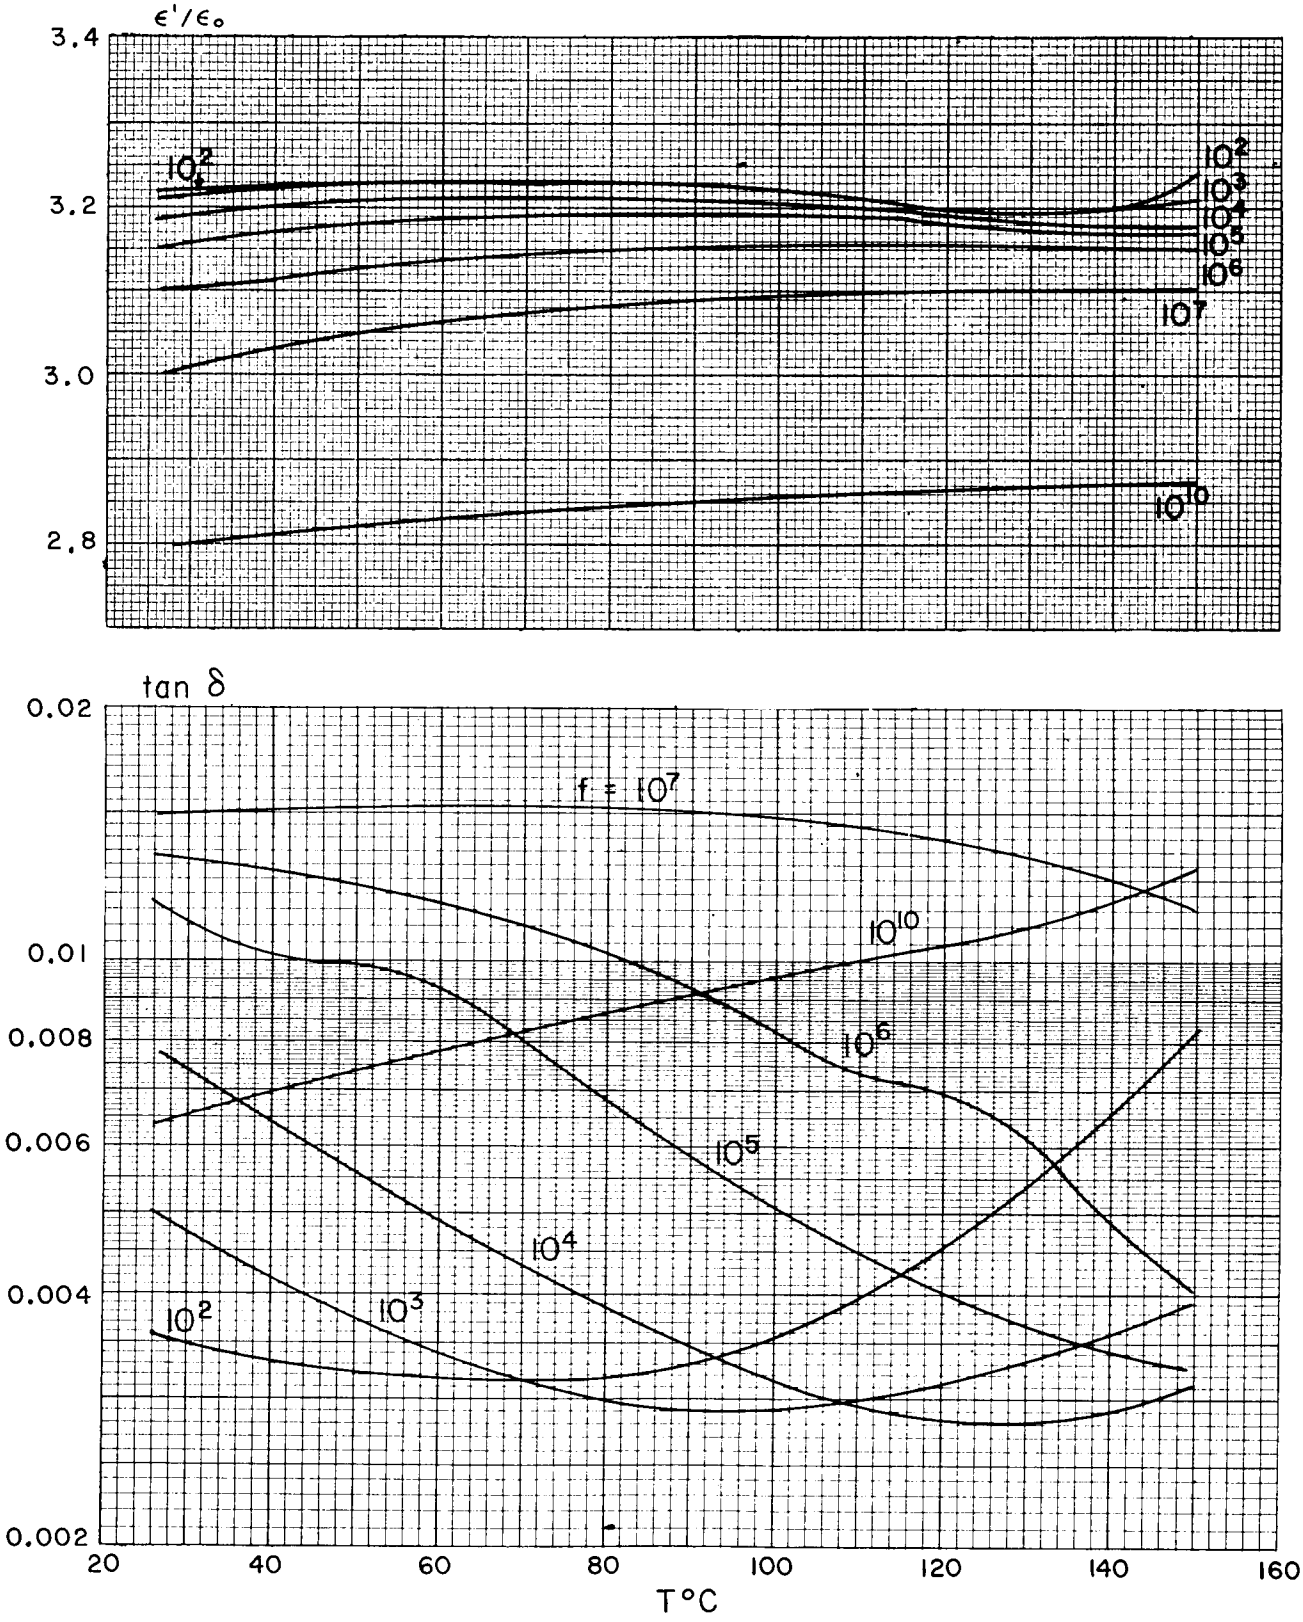


III C. Elastomers

Silicone Rubber SE 450 General Electric, Waterford, N.Y.

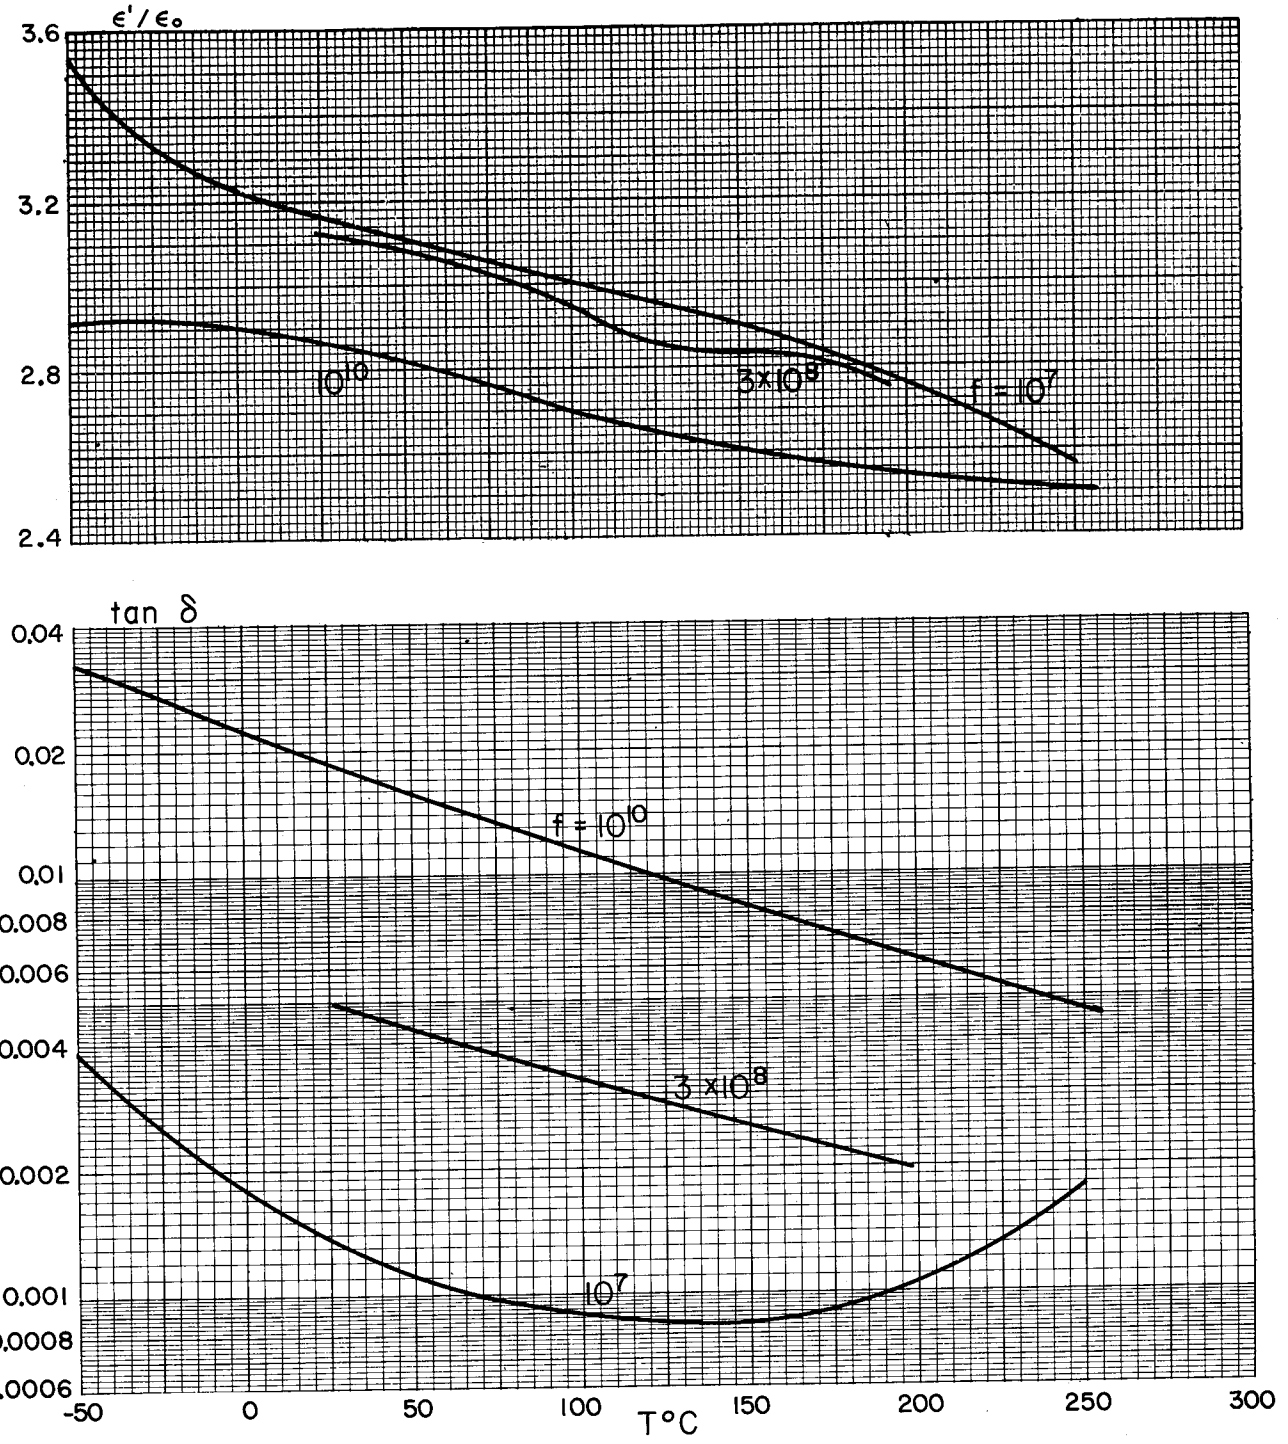


III C. Elastomers

Silicone Rubber SE 460 — General Electric, Waterford, N.Y.

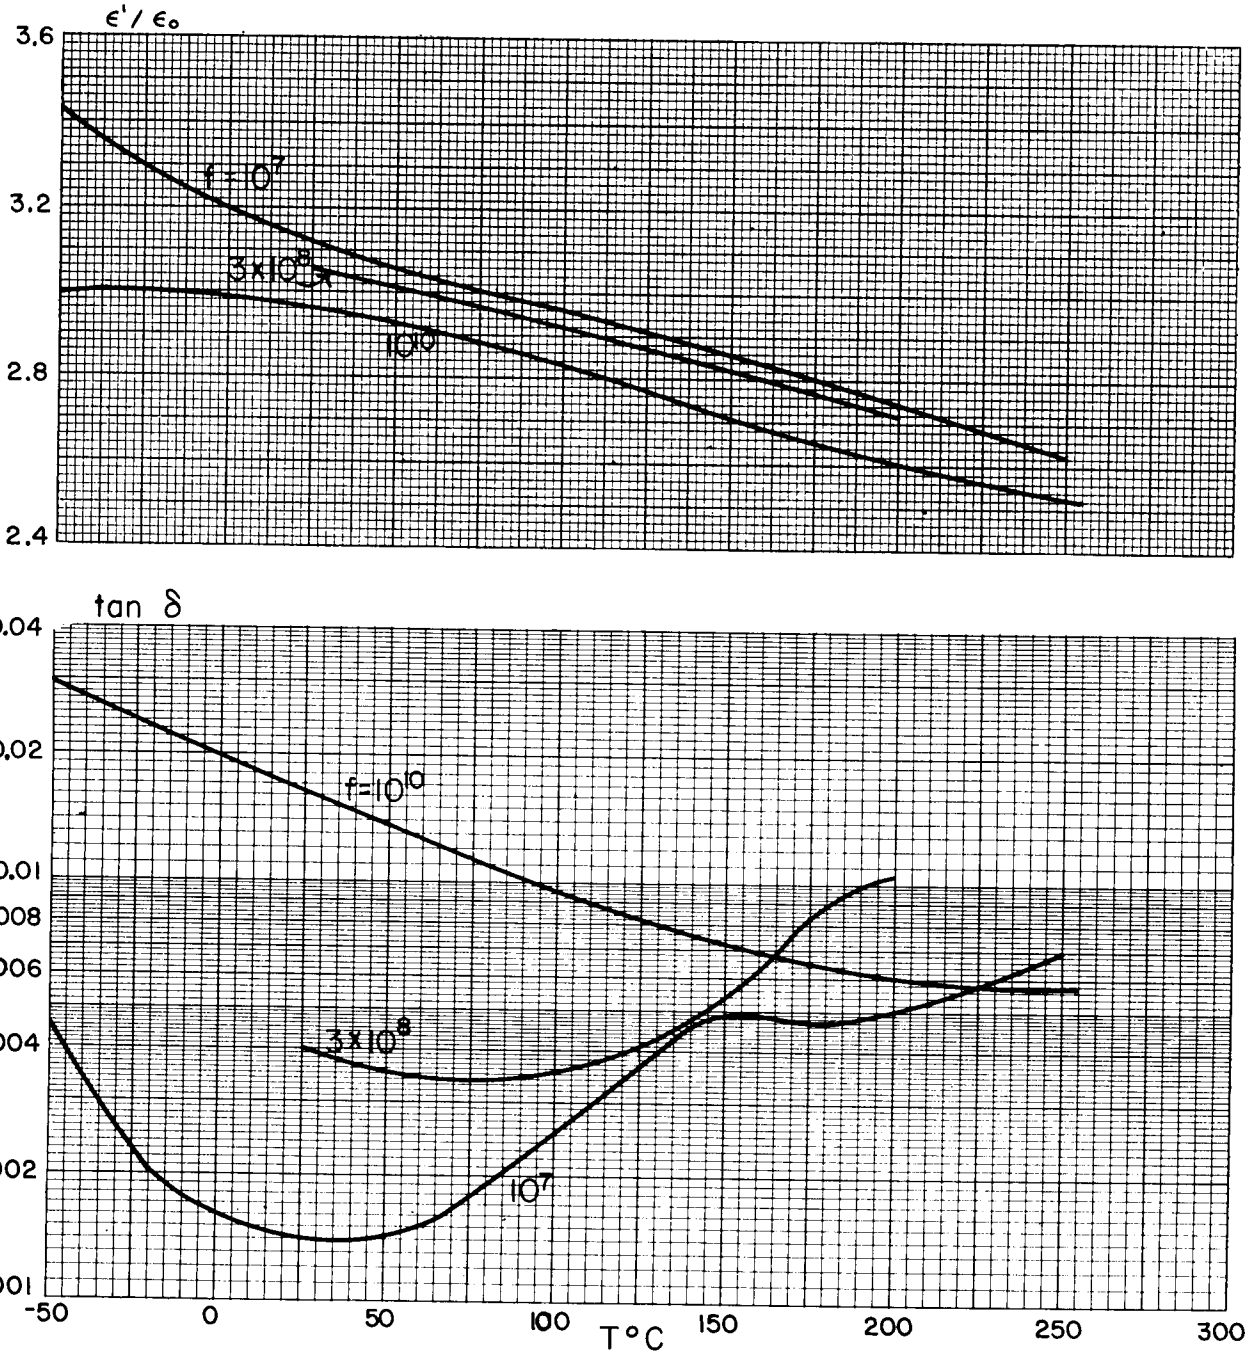

III C. Elastomers


Silicone Rubber SE 972 General Electric, Waterford, N.Y.

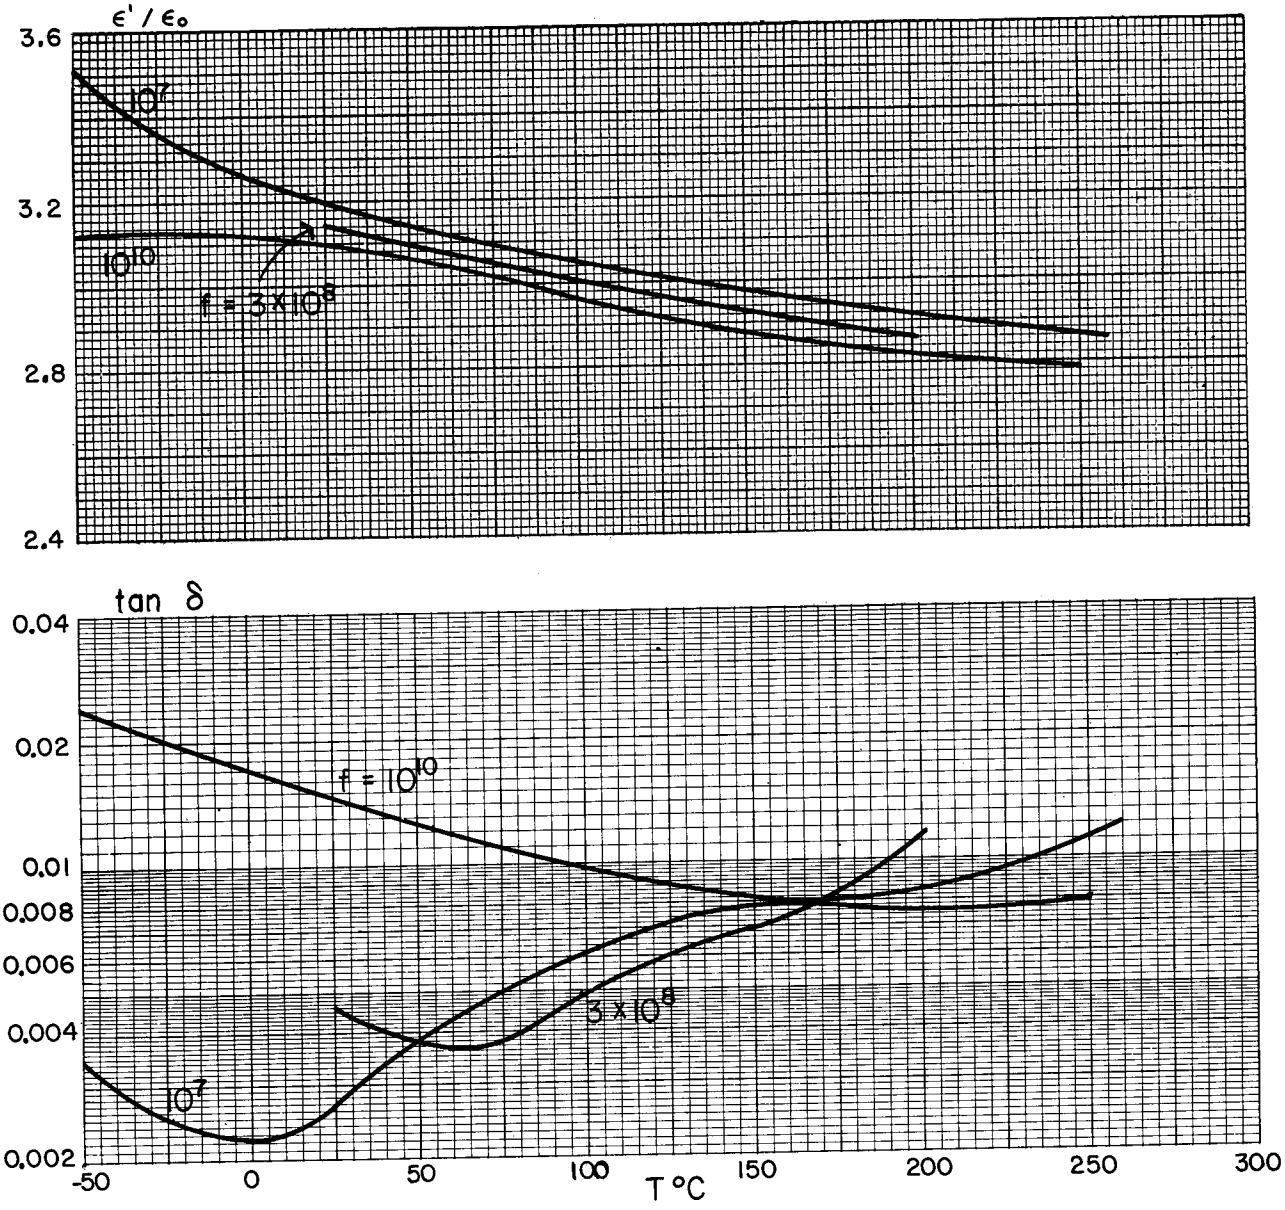

III D. Liquids

"Kel-F" Polymer Oil No. 10


M. W. Kellogg

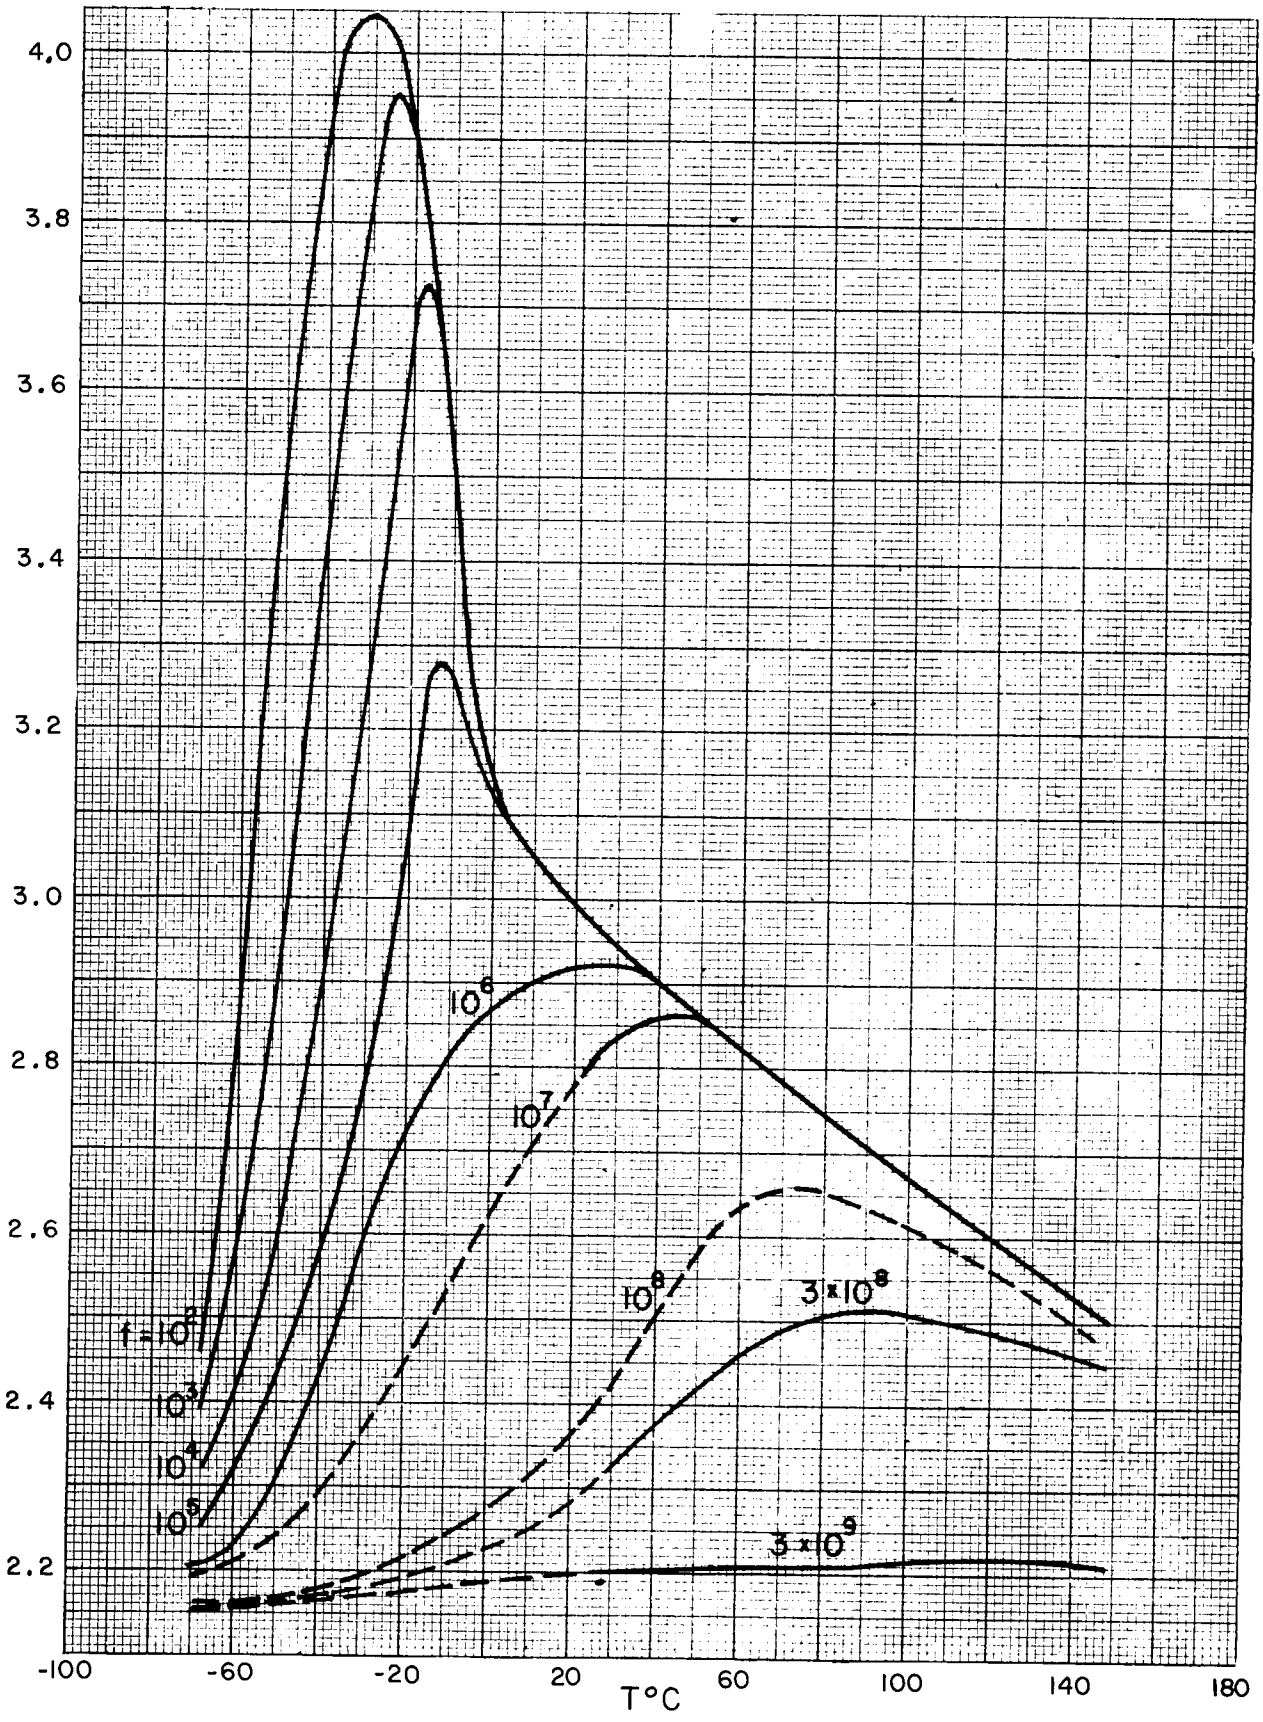

III D. Liquids

"Kel-F" Polymer Oil No. 10

M. W. Kellogg

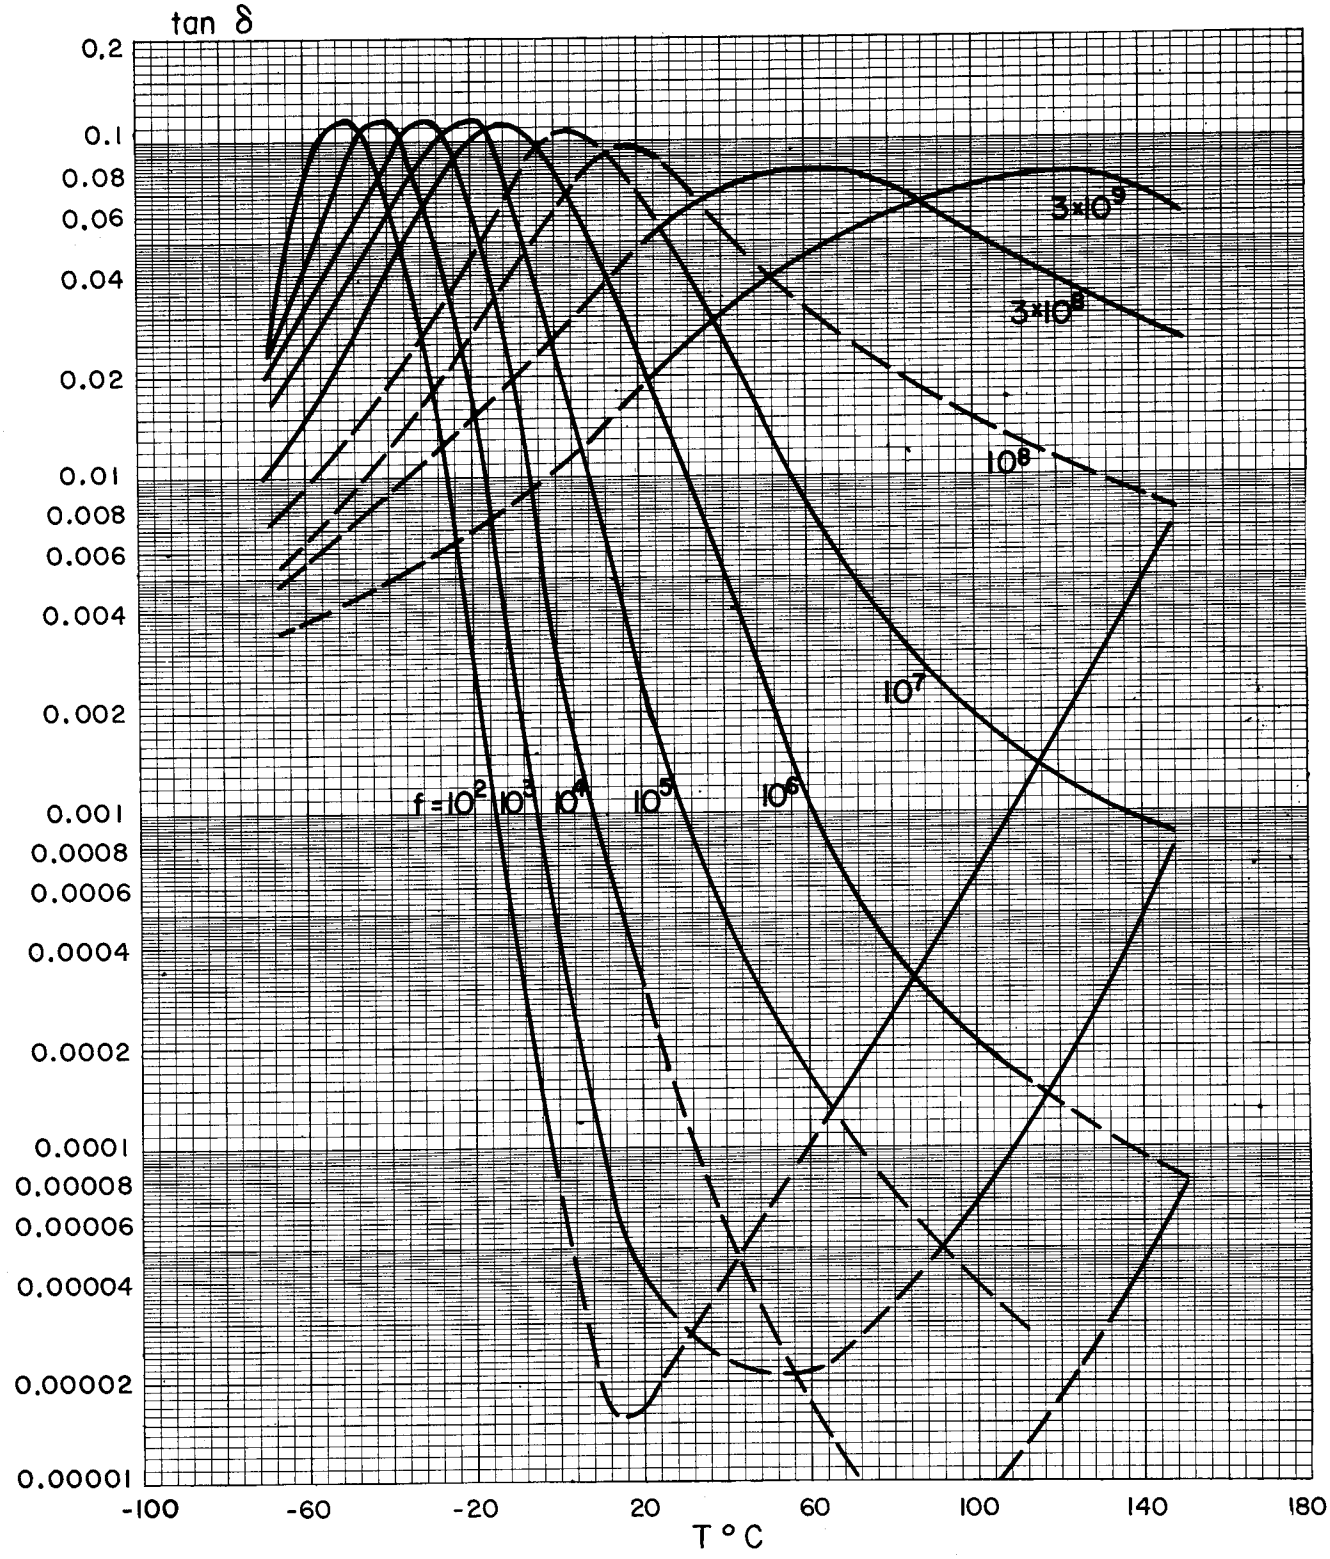

IV. Ferromagnetic Dielectrics

Complete evaluation of a magnetic material for both scientific study and engineering design requires measurement of κ^* and κ^*_m vs. frequency, temperature, a-c field strength, and d-c bias. Phenomena of interest range from the very slow changes in magnetization with time at low temperatures to the instantaneous permeability at high microwave power.

In this section we have limited our data to κ^* and κ^*_m vs. frequency at low a-c field strengths and fixed temperatures and to the quasi-static hysteresis loops at room temperature. At frequencies up to 10 Mc we have also plotted κ''_m/κ'_m, a figure of merit for core materials. In the literature this is designated as $1/\mu'Q$ and called loss factor.

For many of the laboratory materials and some of the commercial materials other measurements have been made such as:

D-c conductivity vs. temperature,

κ^*, κ^*_m vs. temperature at fixed frequencies, low fields,

κ^*, κ^*_m vs. field strength at fixed frequencies and temperatures.

Some of this information is included in Tech. Rep. 97, a revised version of which will be published in Revs. Mod. Phys., July, 1957, and in a forthcoming technical report by D. J. Epstein. Other data are available from the measurements group file.


Details of the preparation of ferrites have been given in Tech. Rep. 78 by G. Economos.

Unless otherwise noted, measurements were taken at $26^oC \pm 1$. σ is given in mho/m.


Low-frequency dielectric measurements marked ⊗ were four-terminal measurements made to eliminate electrode effects.

IV A. Low Field-Strength Data at Fixed Temperatures as a Function of Frequency


1. Nickel Ferrite, Single Crystal

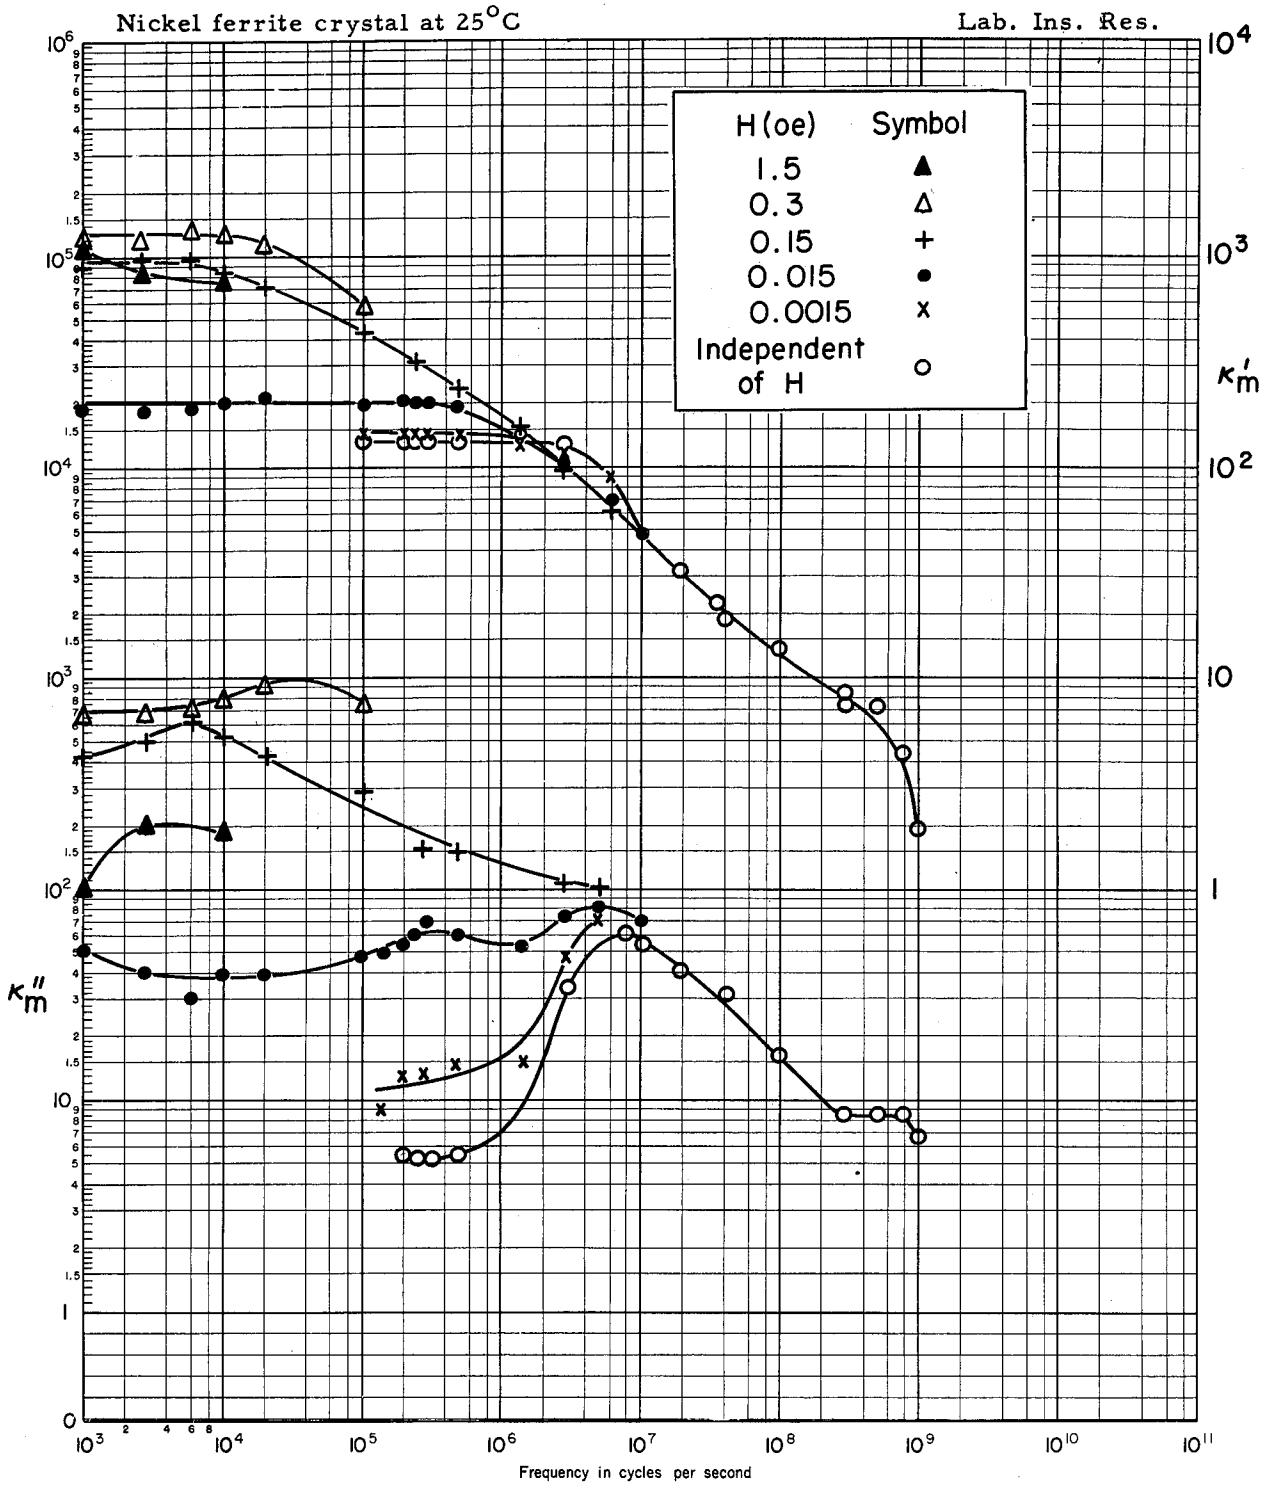


IV A 1. Nickel Ferrite, Single Crystal

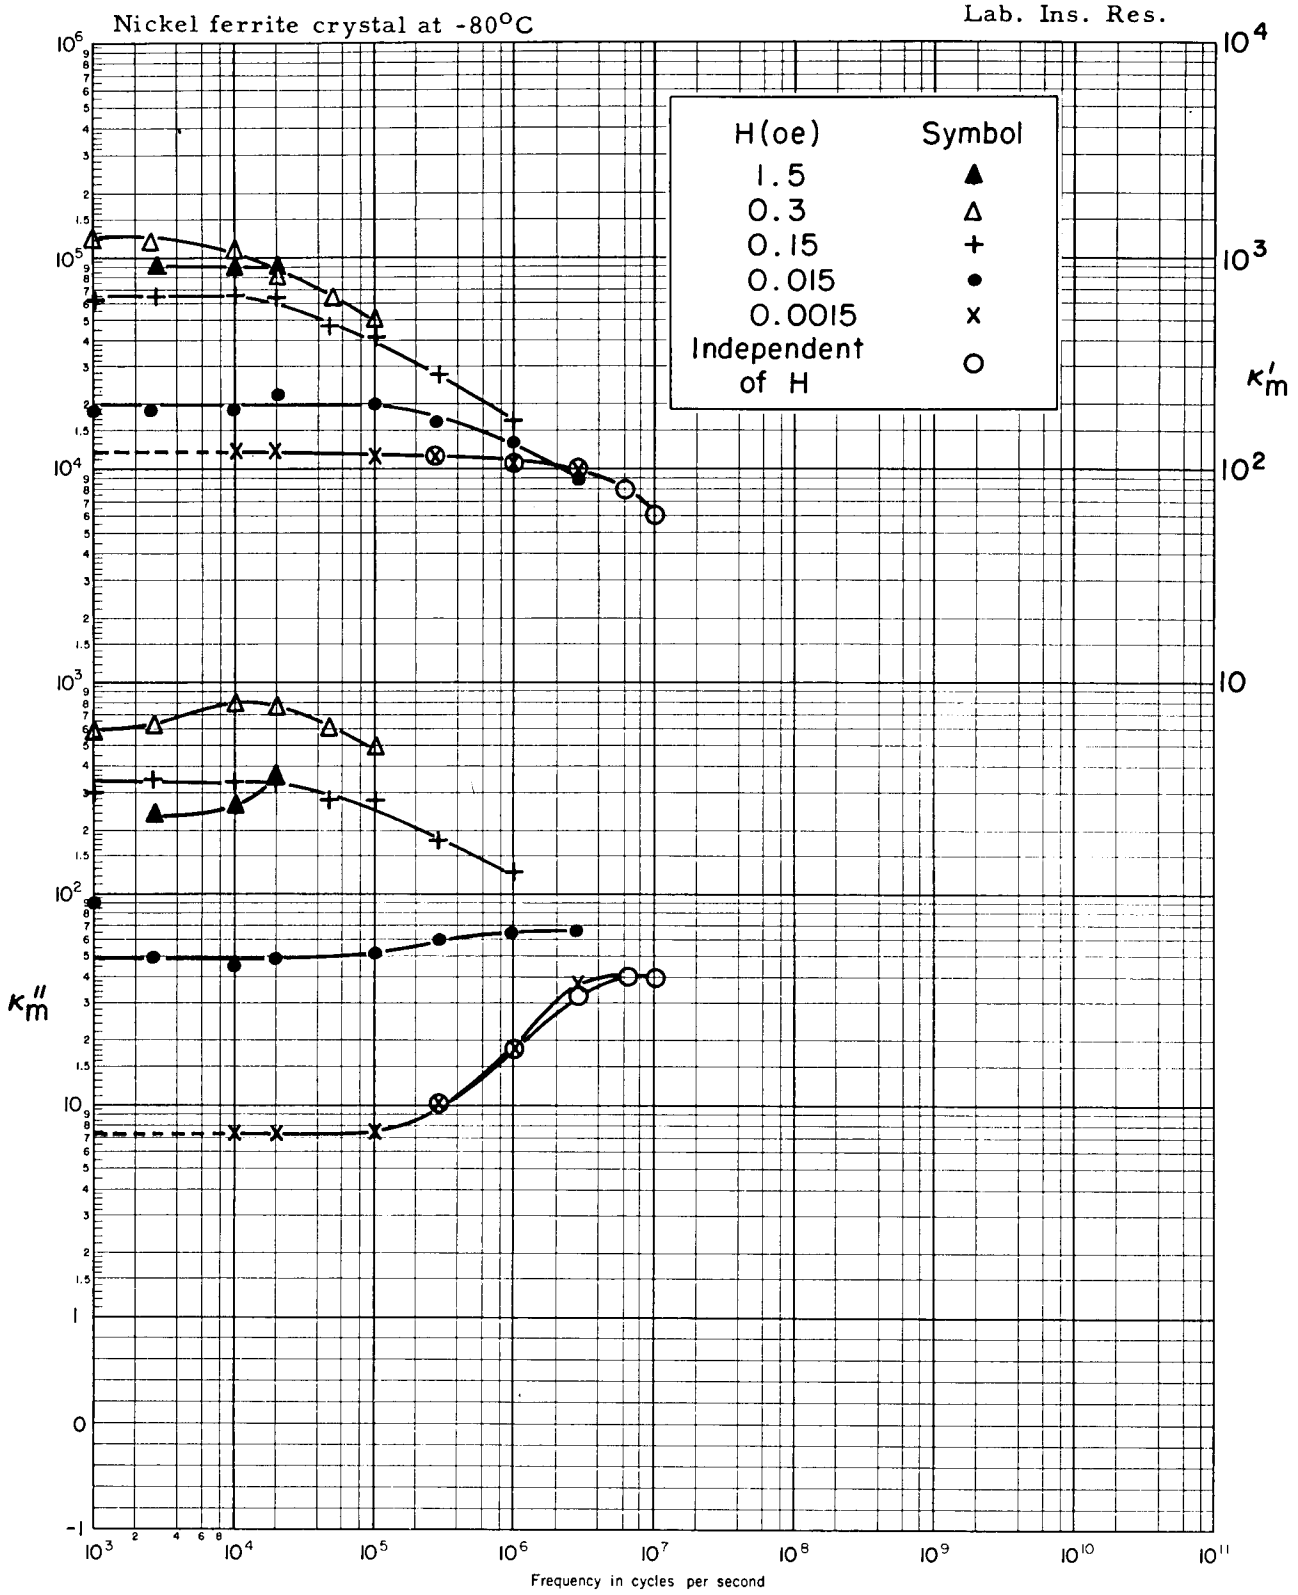


IV A 1. Nickel Ferrite, Single Crystal

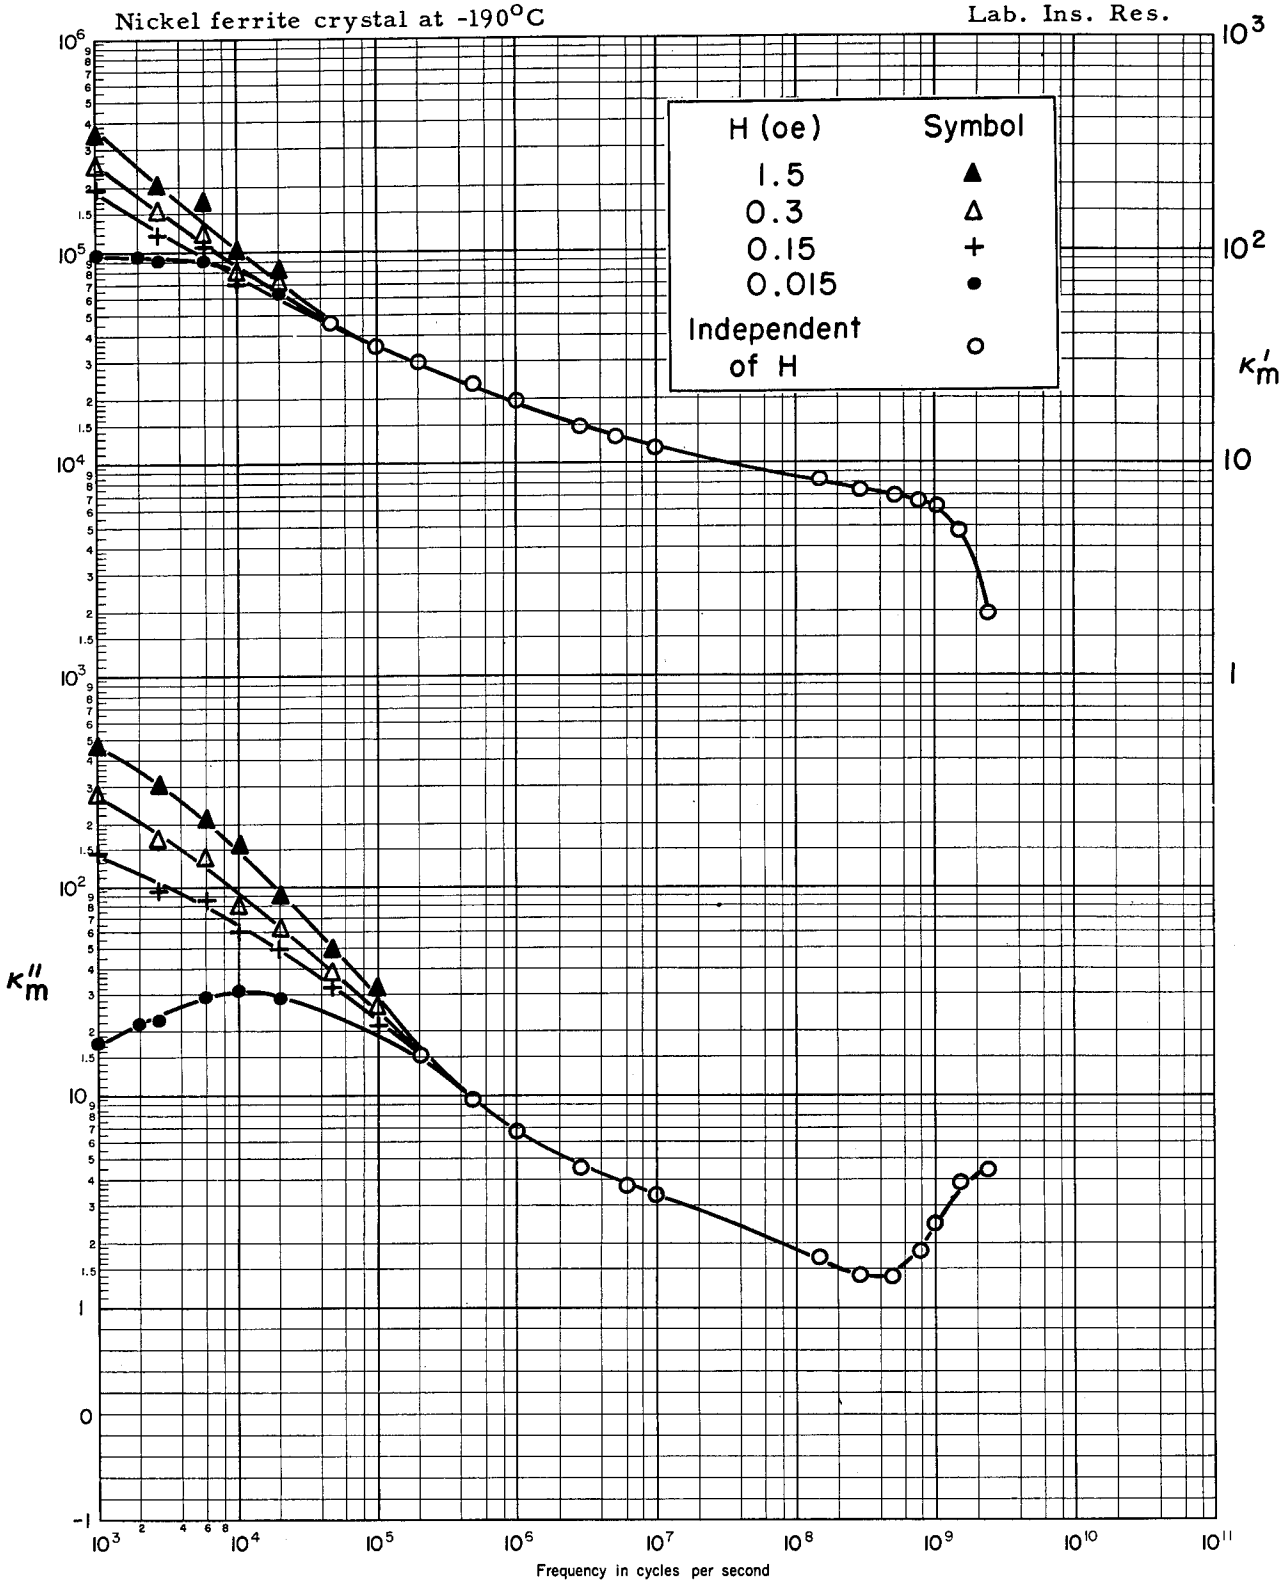


IV A 2. Cobalt Ferrite, High Density Ceramic

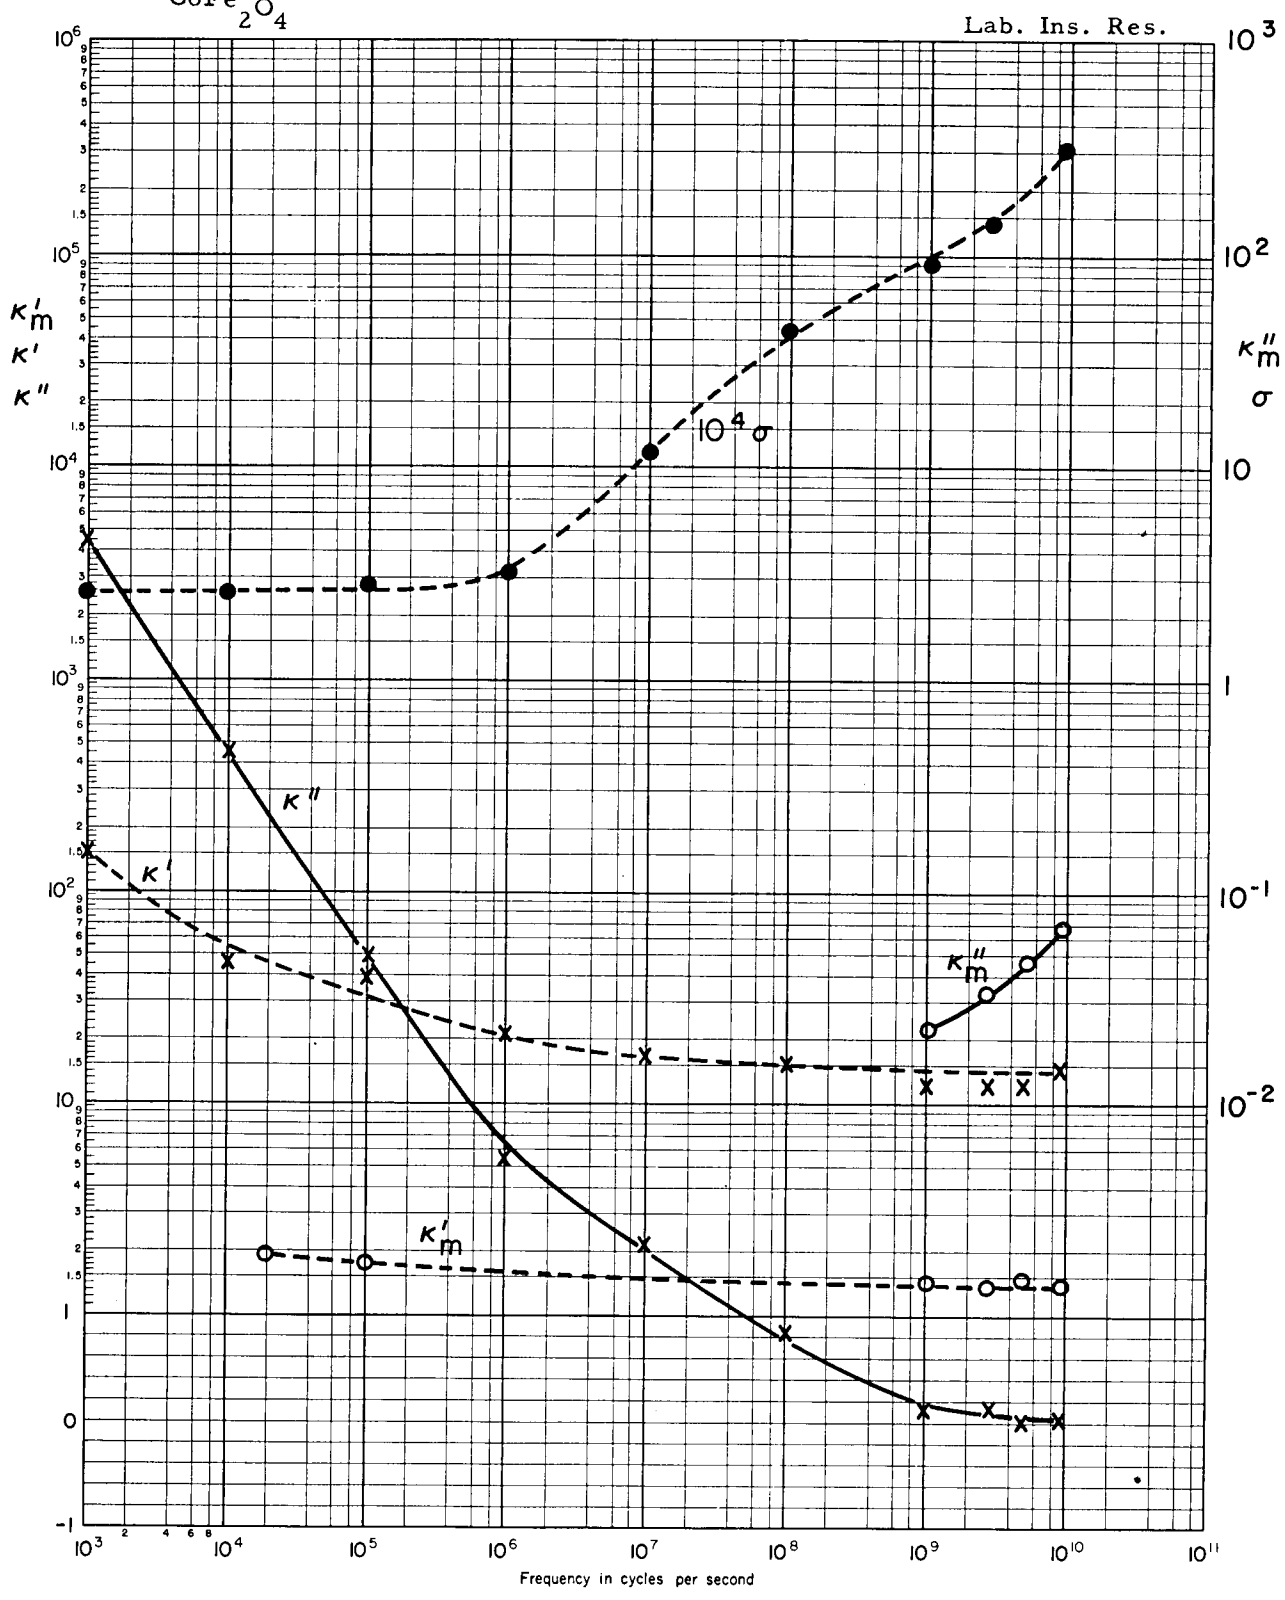


IV A 3. Lithium-Nickel Ferrite Ceramic

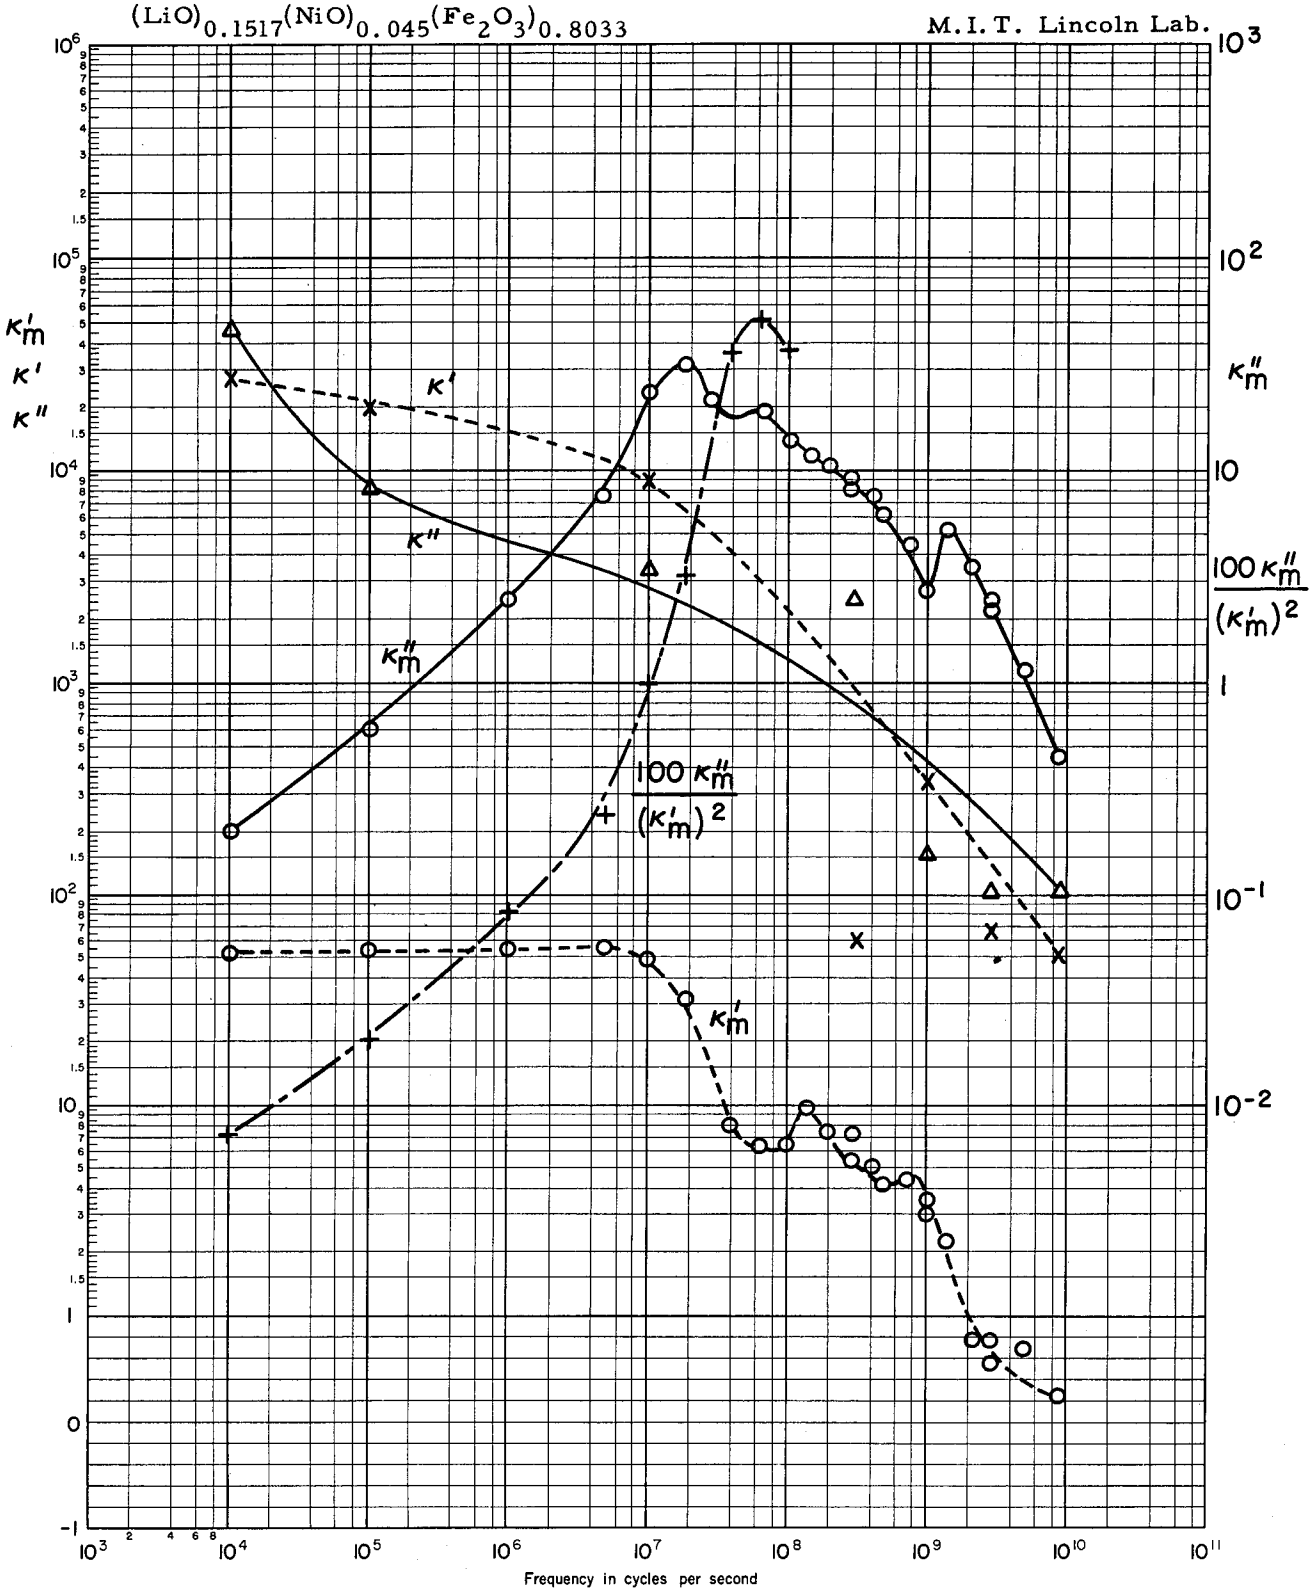


IV A 4. Magnesium Ferrite, High Density Ceramic

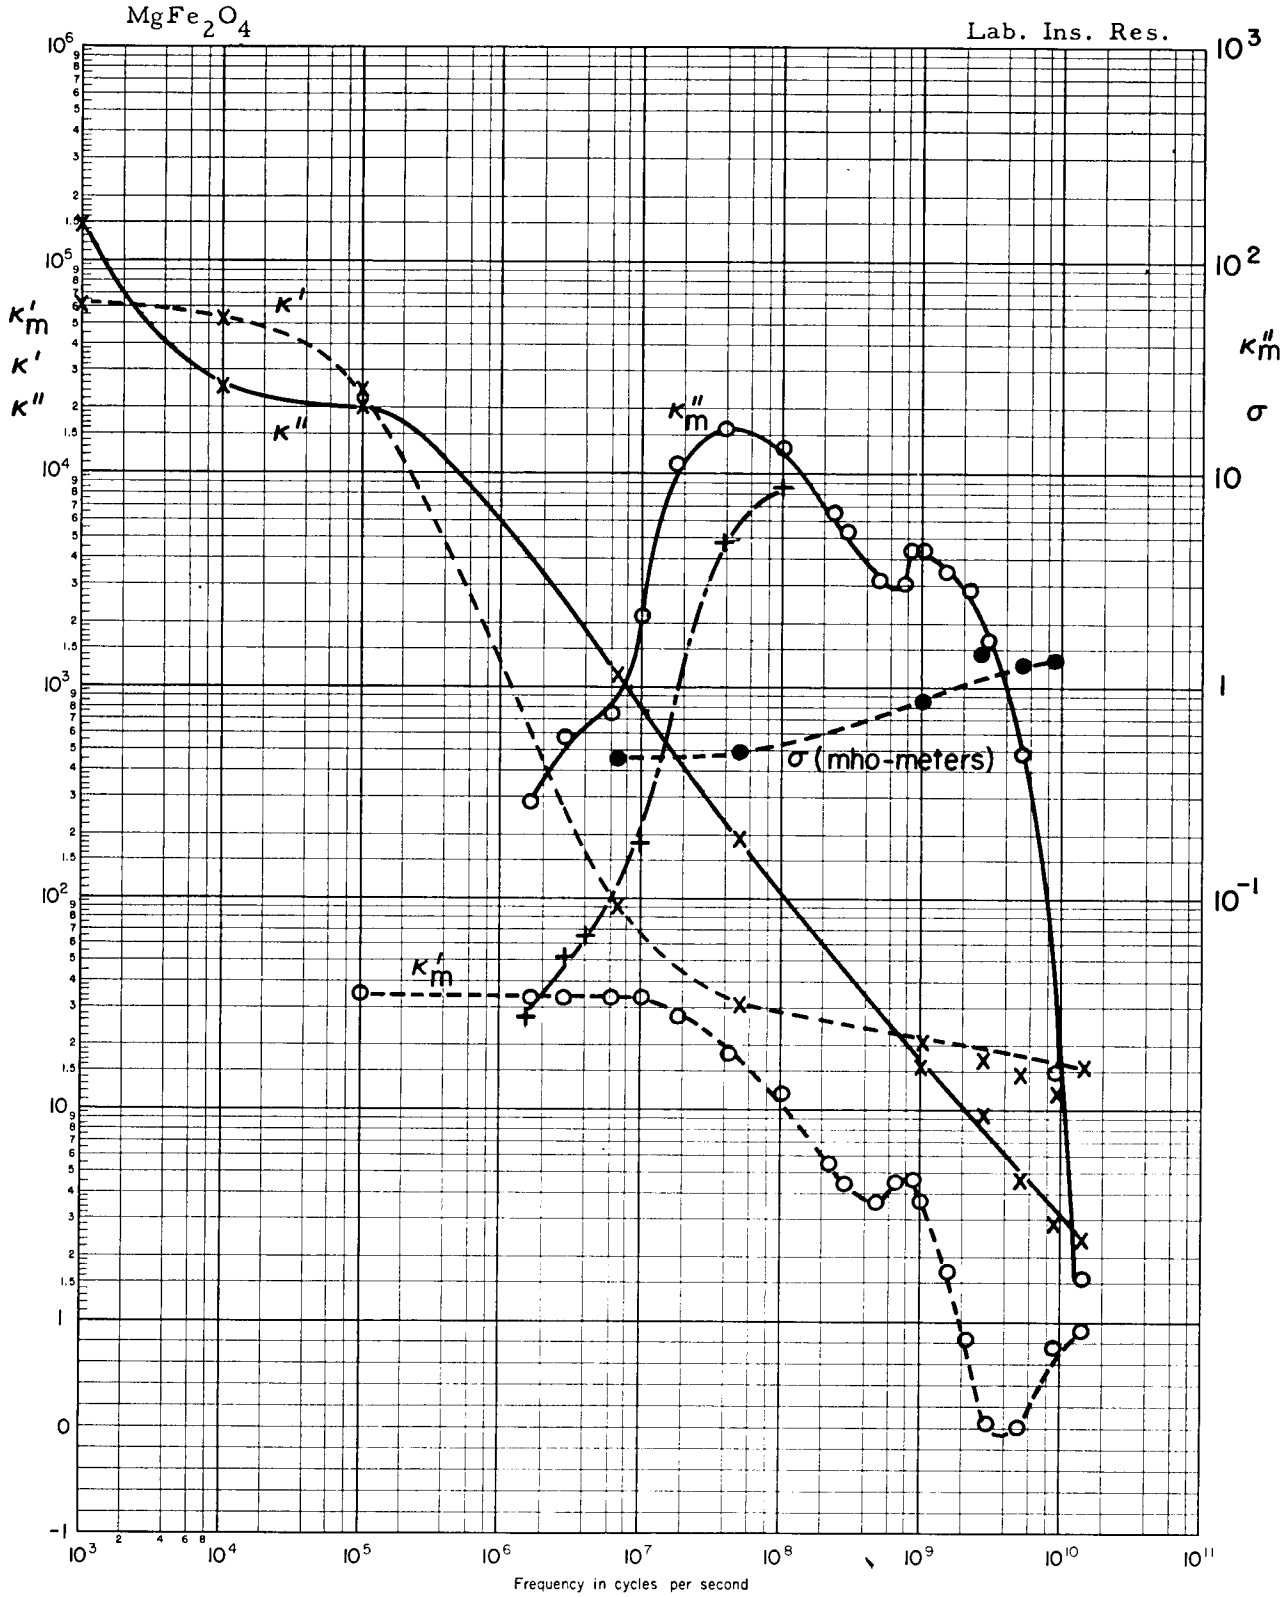


IV A 5. Magnesium Manganese Ferrite Ceramics

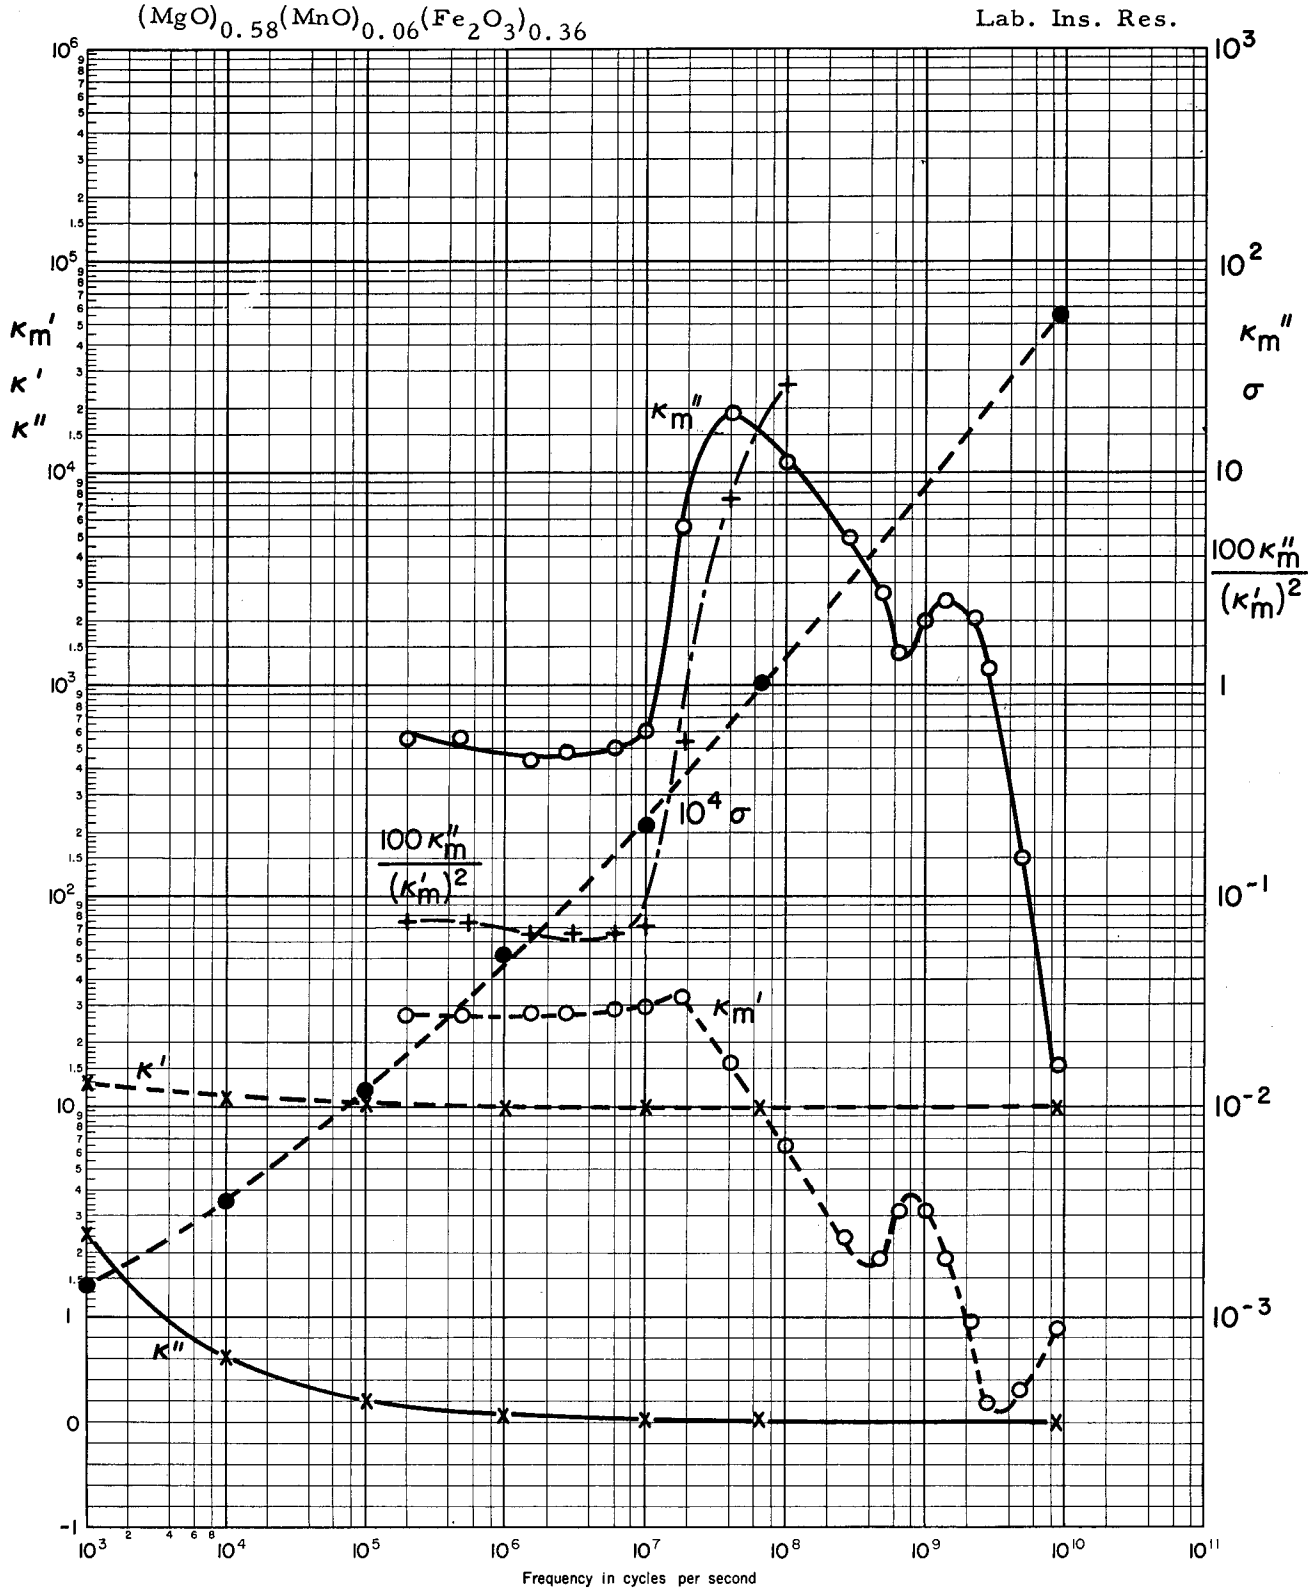


IV A 5. Magnesium-Manganese Ferrite Ceramics

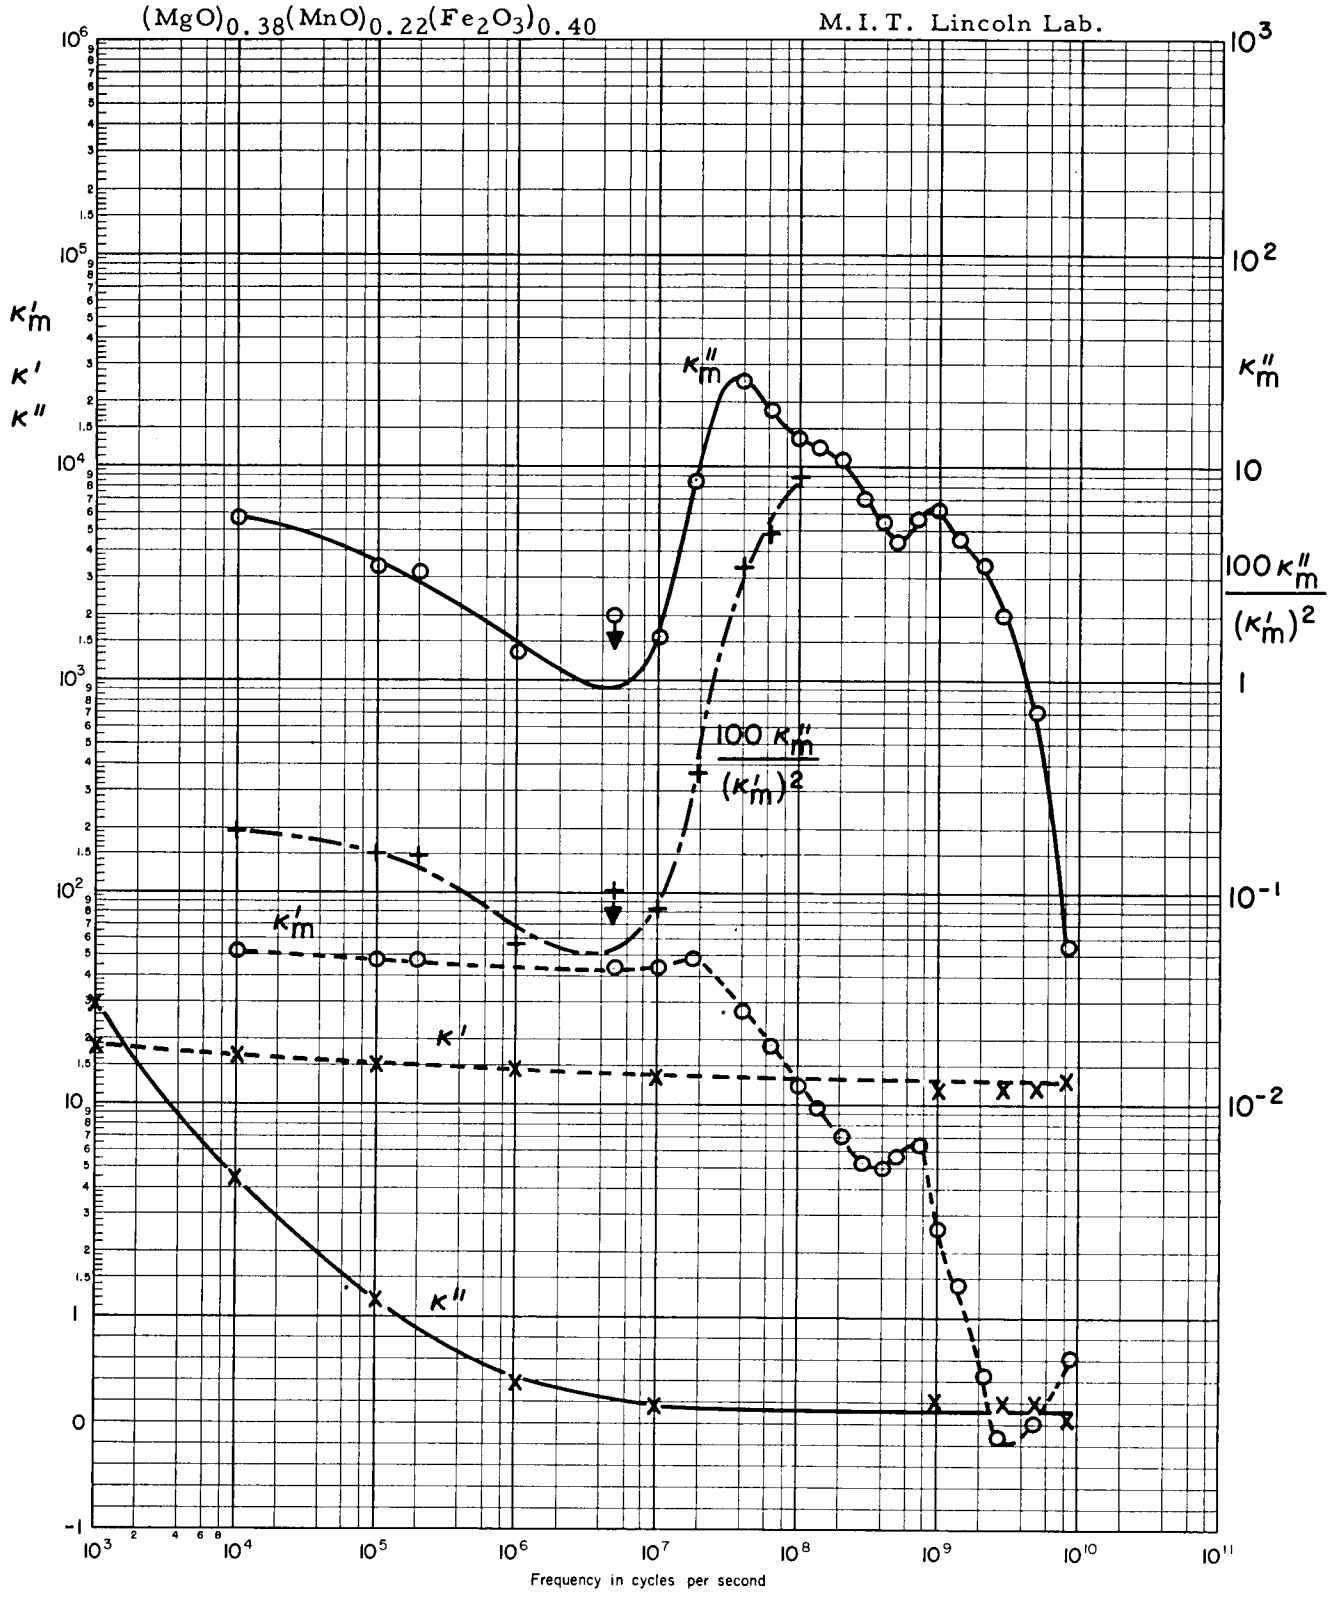


IV A 6. Magnesium-Manganese-Zinc Ferrite Ceramic

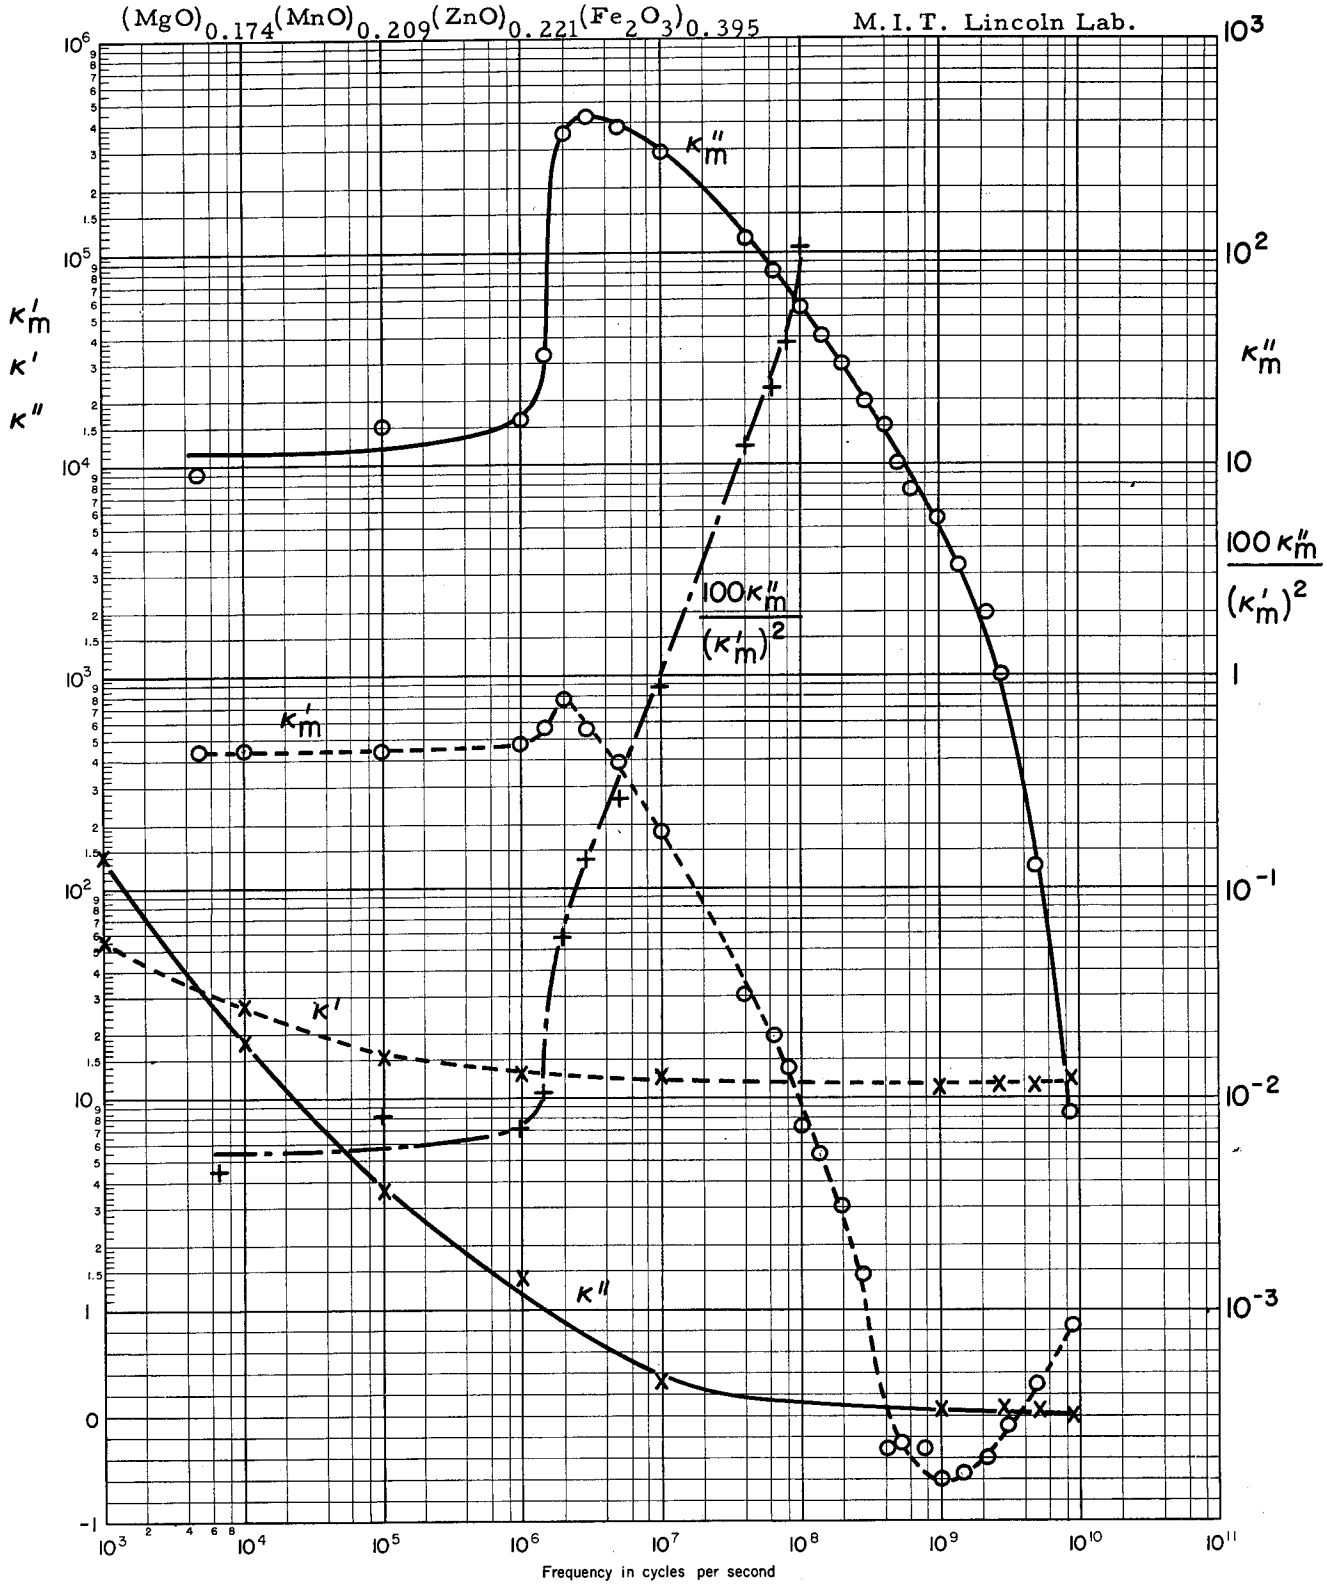


IV A 7. Nickel Ferrite, High Density Ceramic

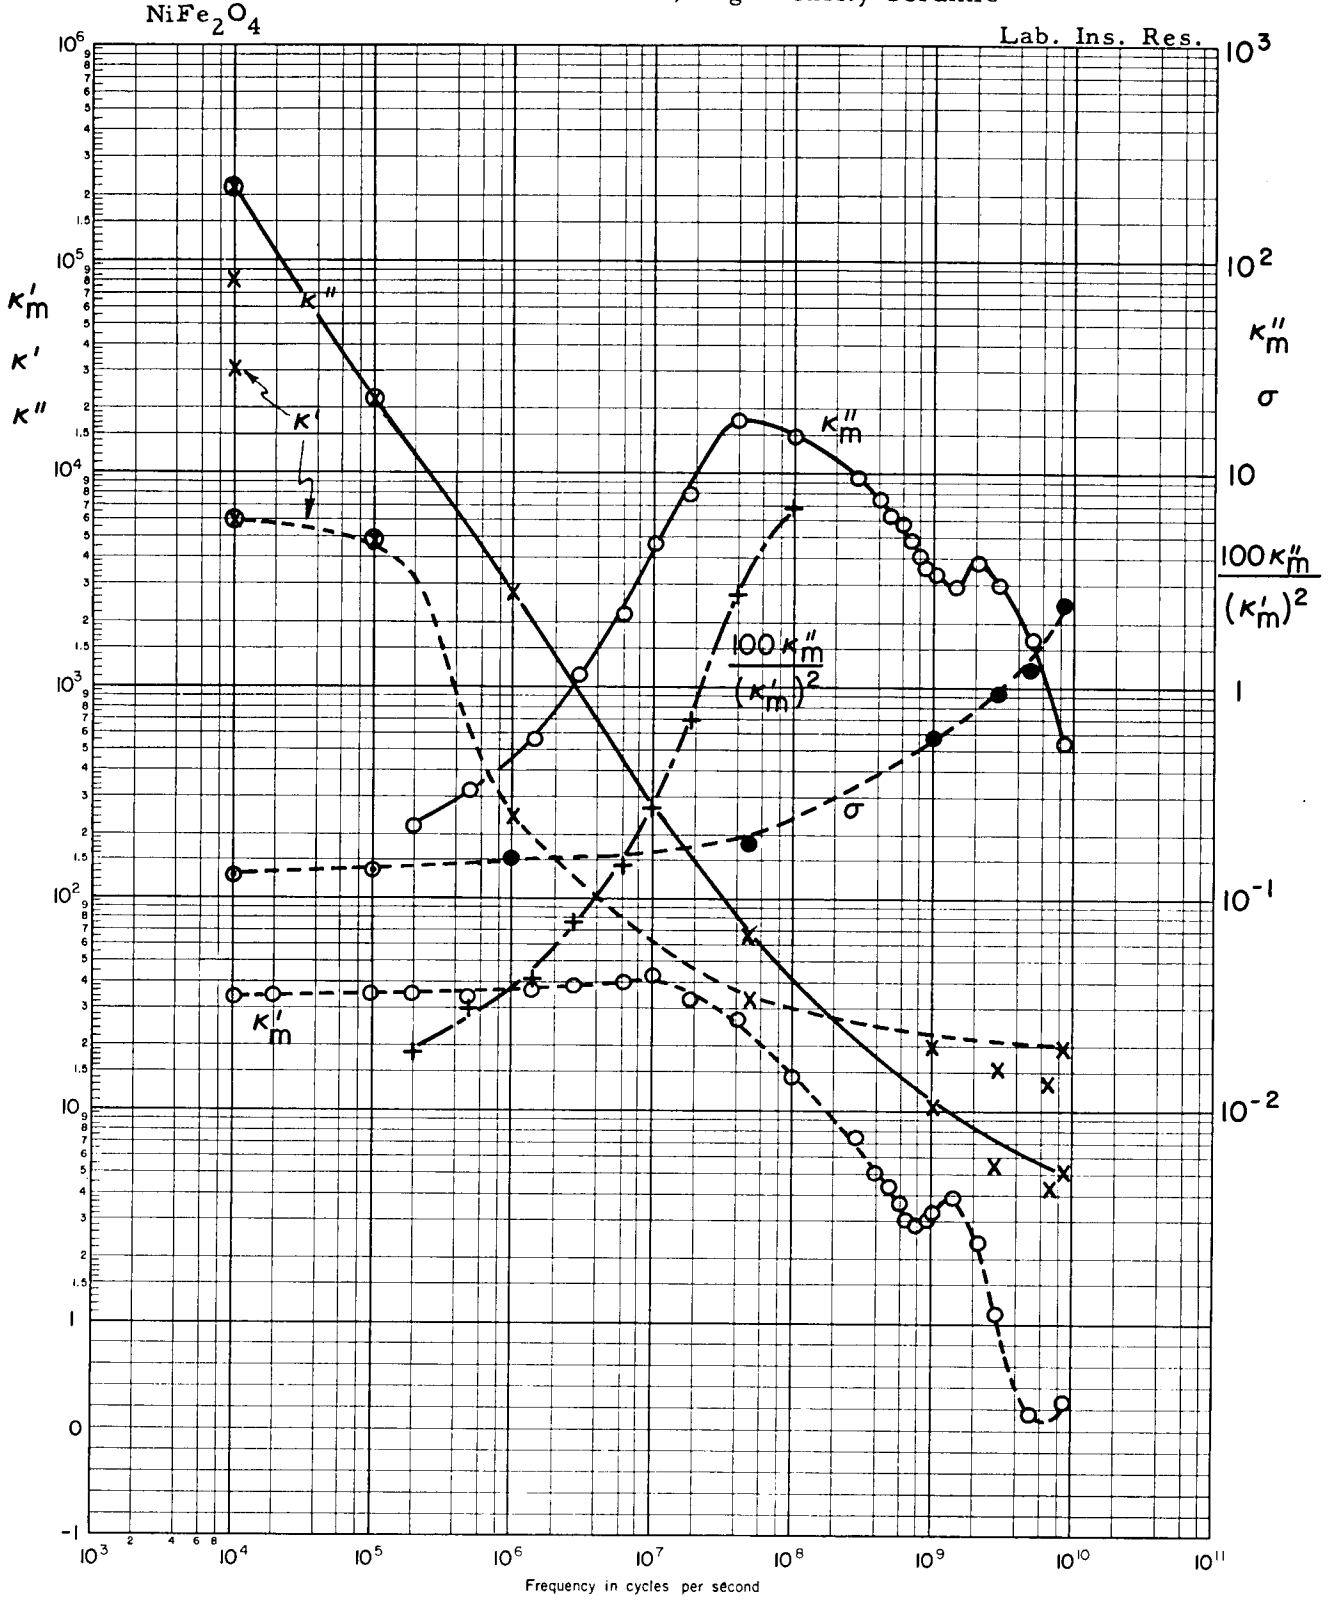


IV A 7. Nickel Ferrite, High Density Ceramic

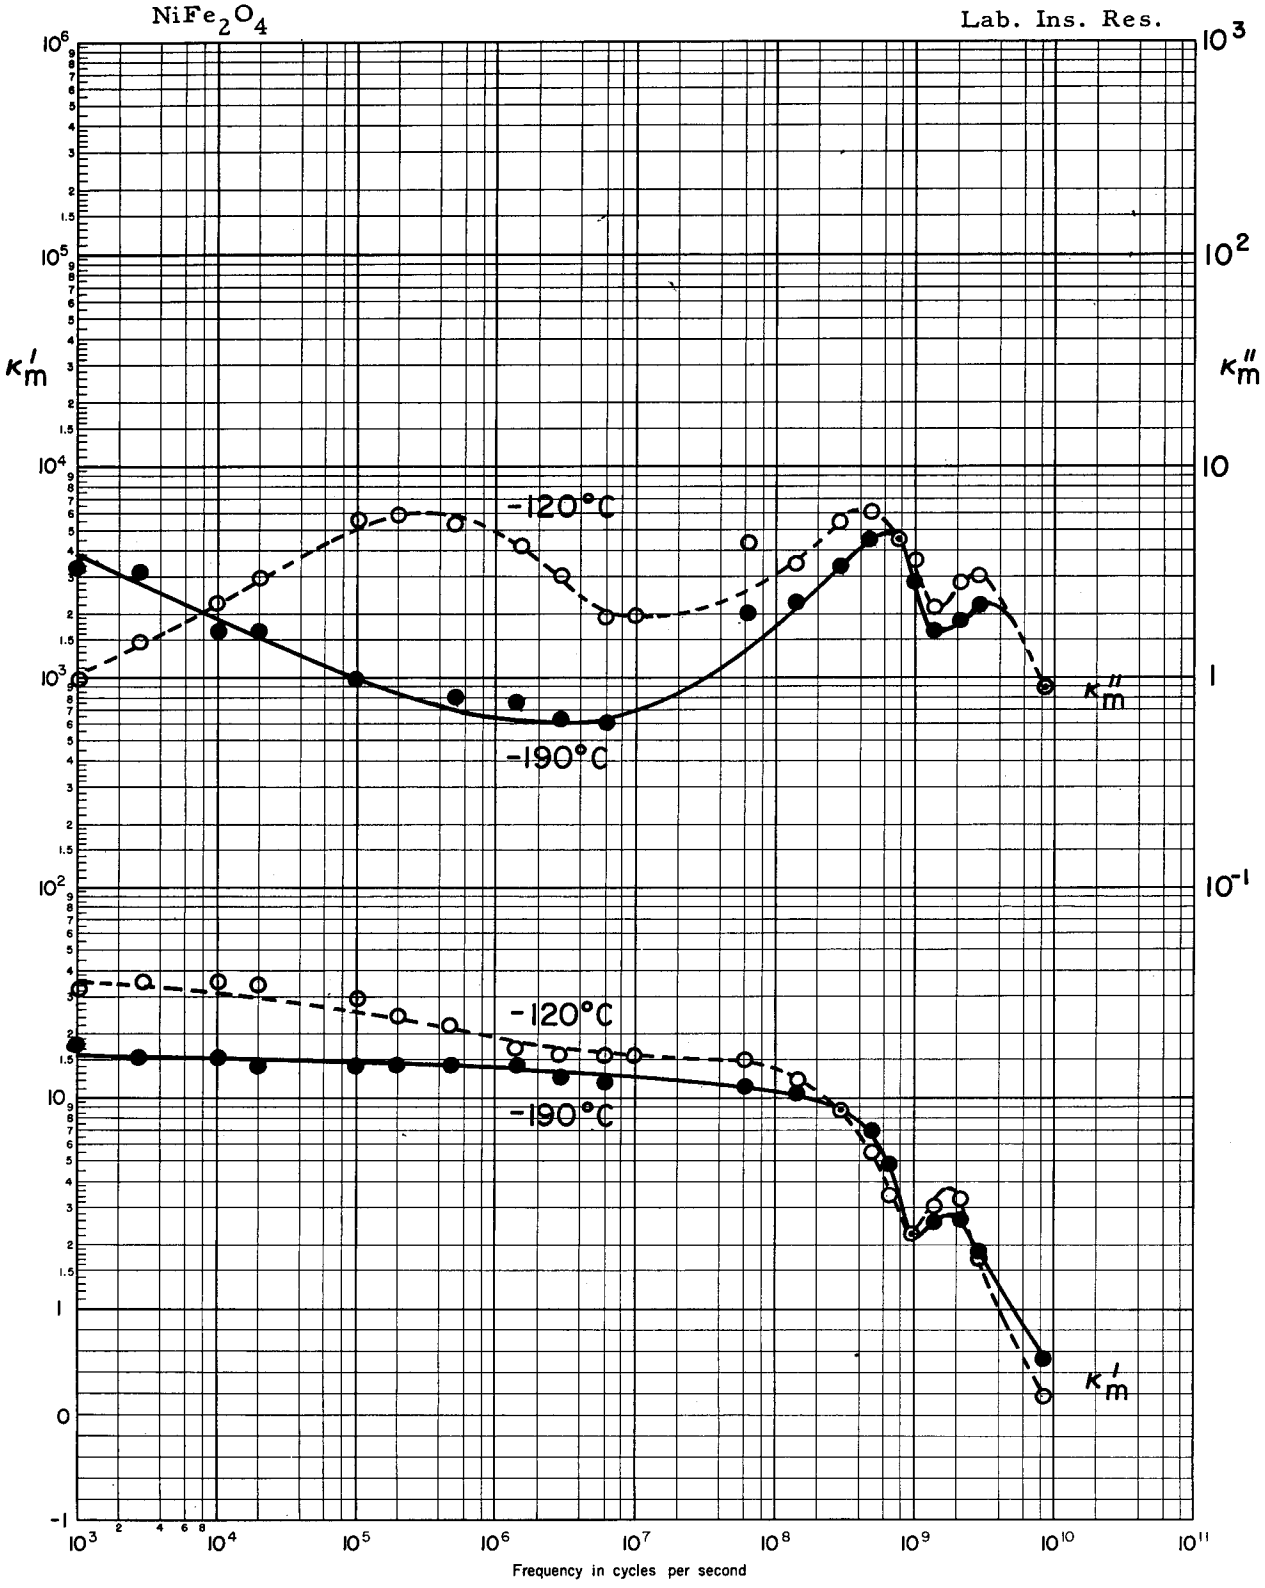


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

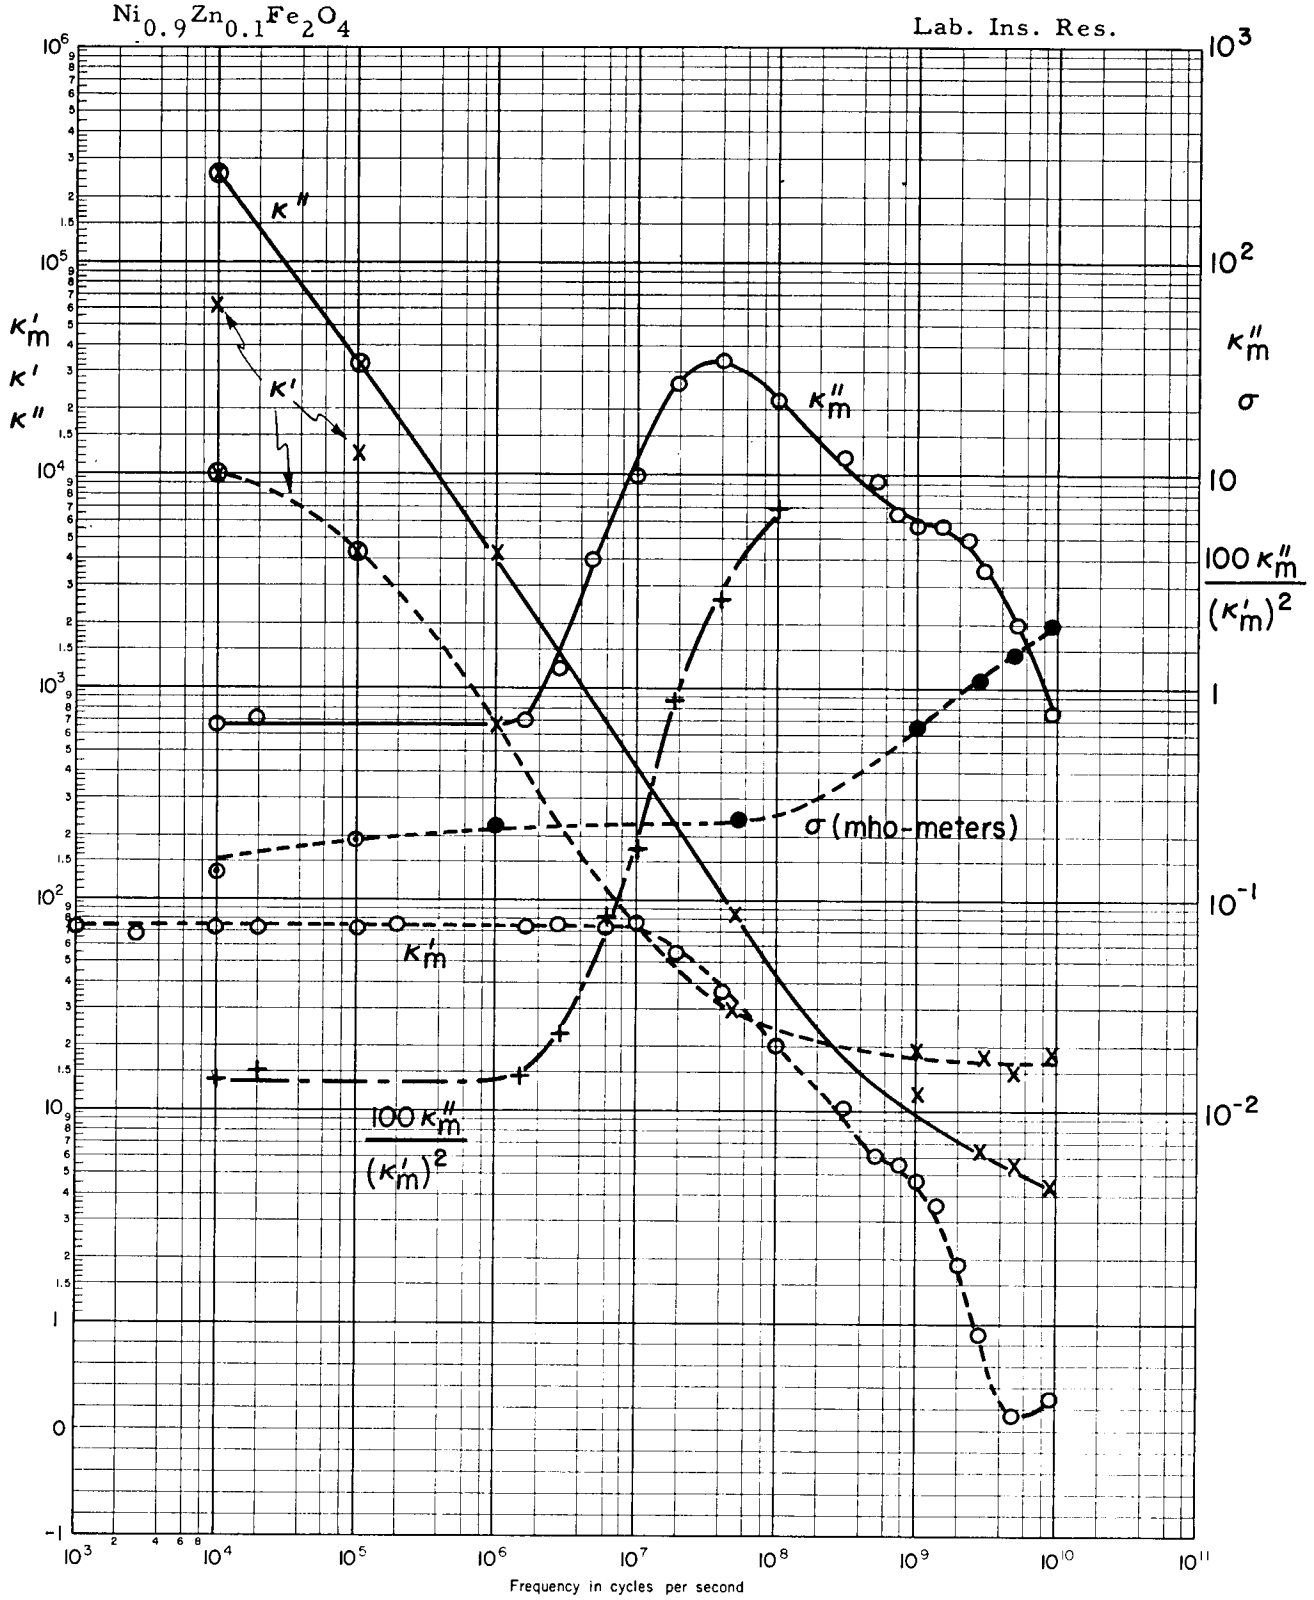


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

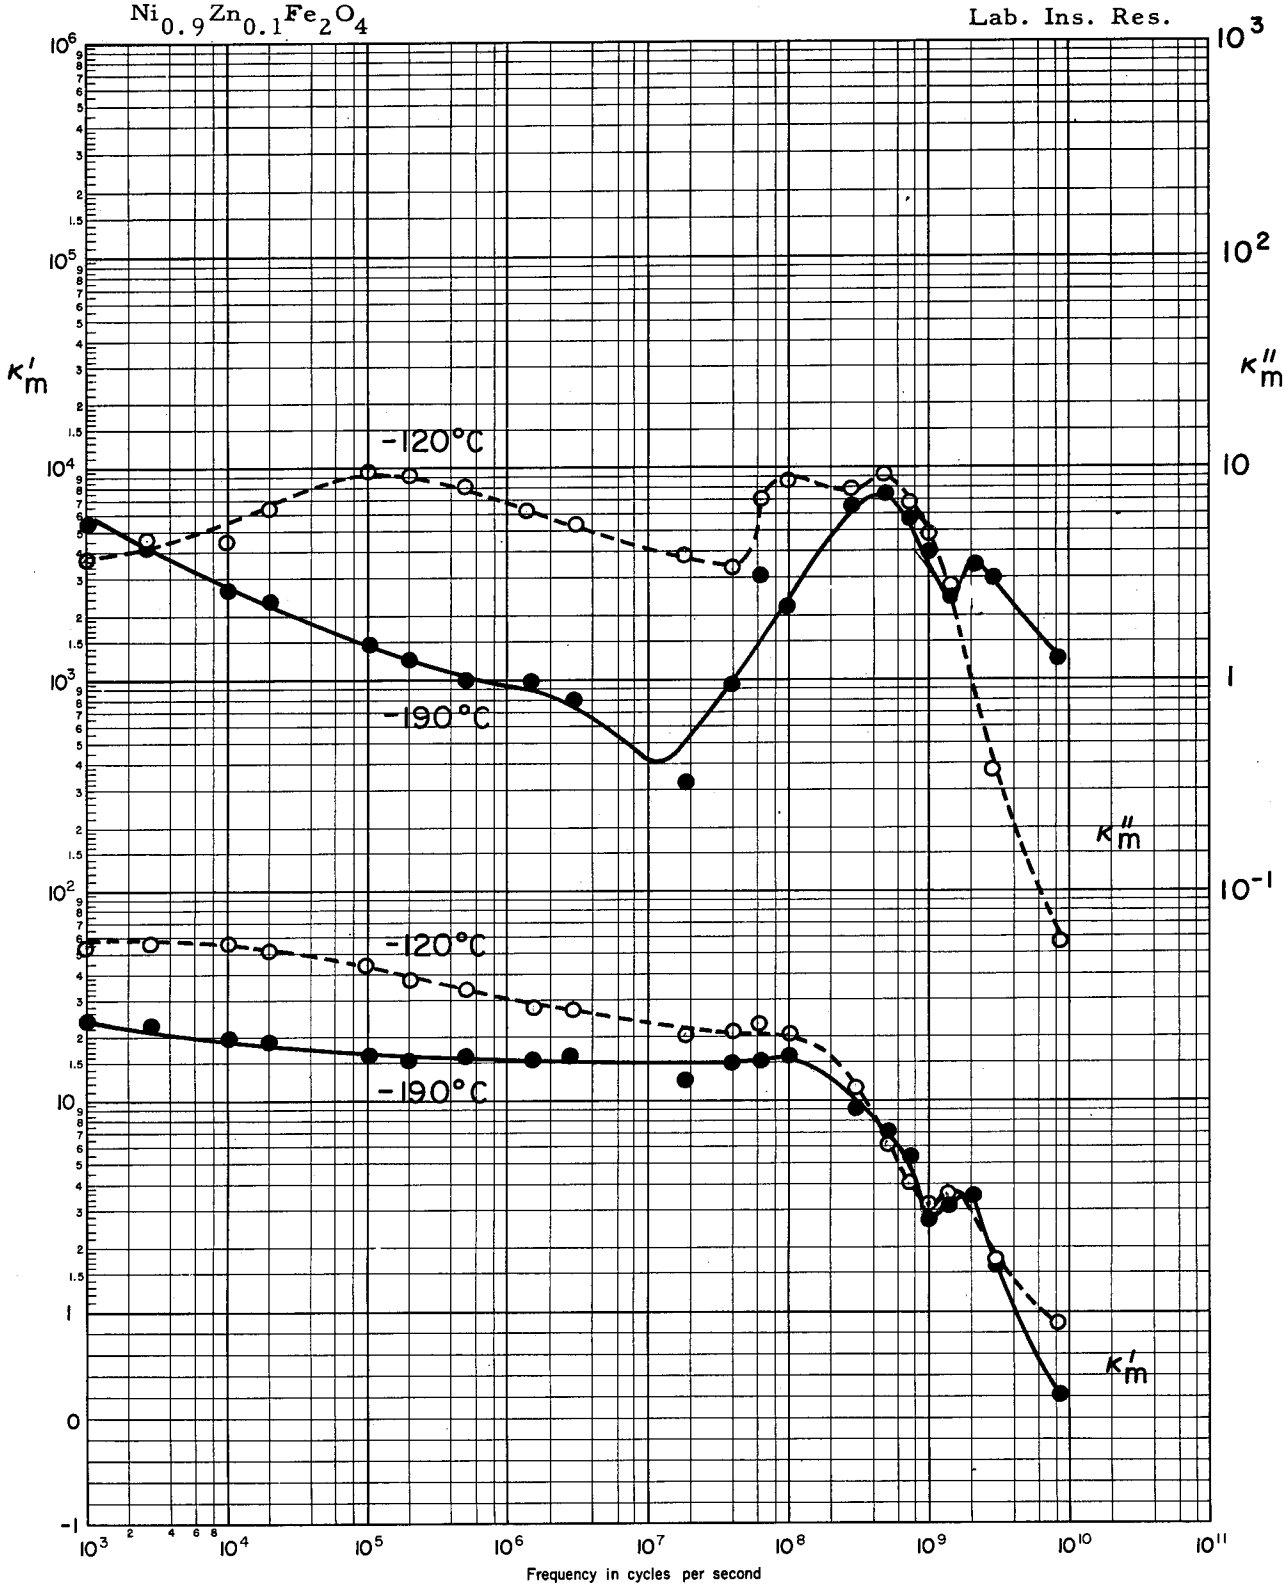


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

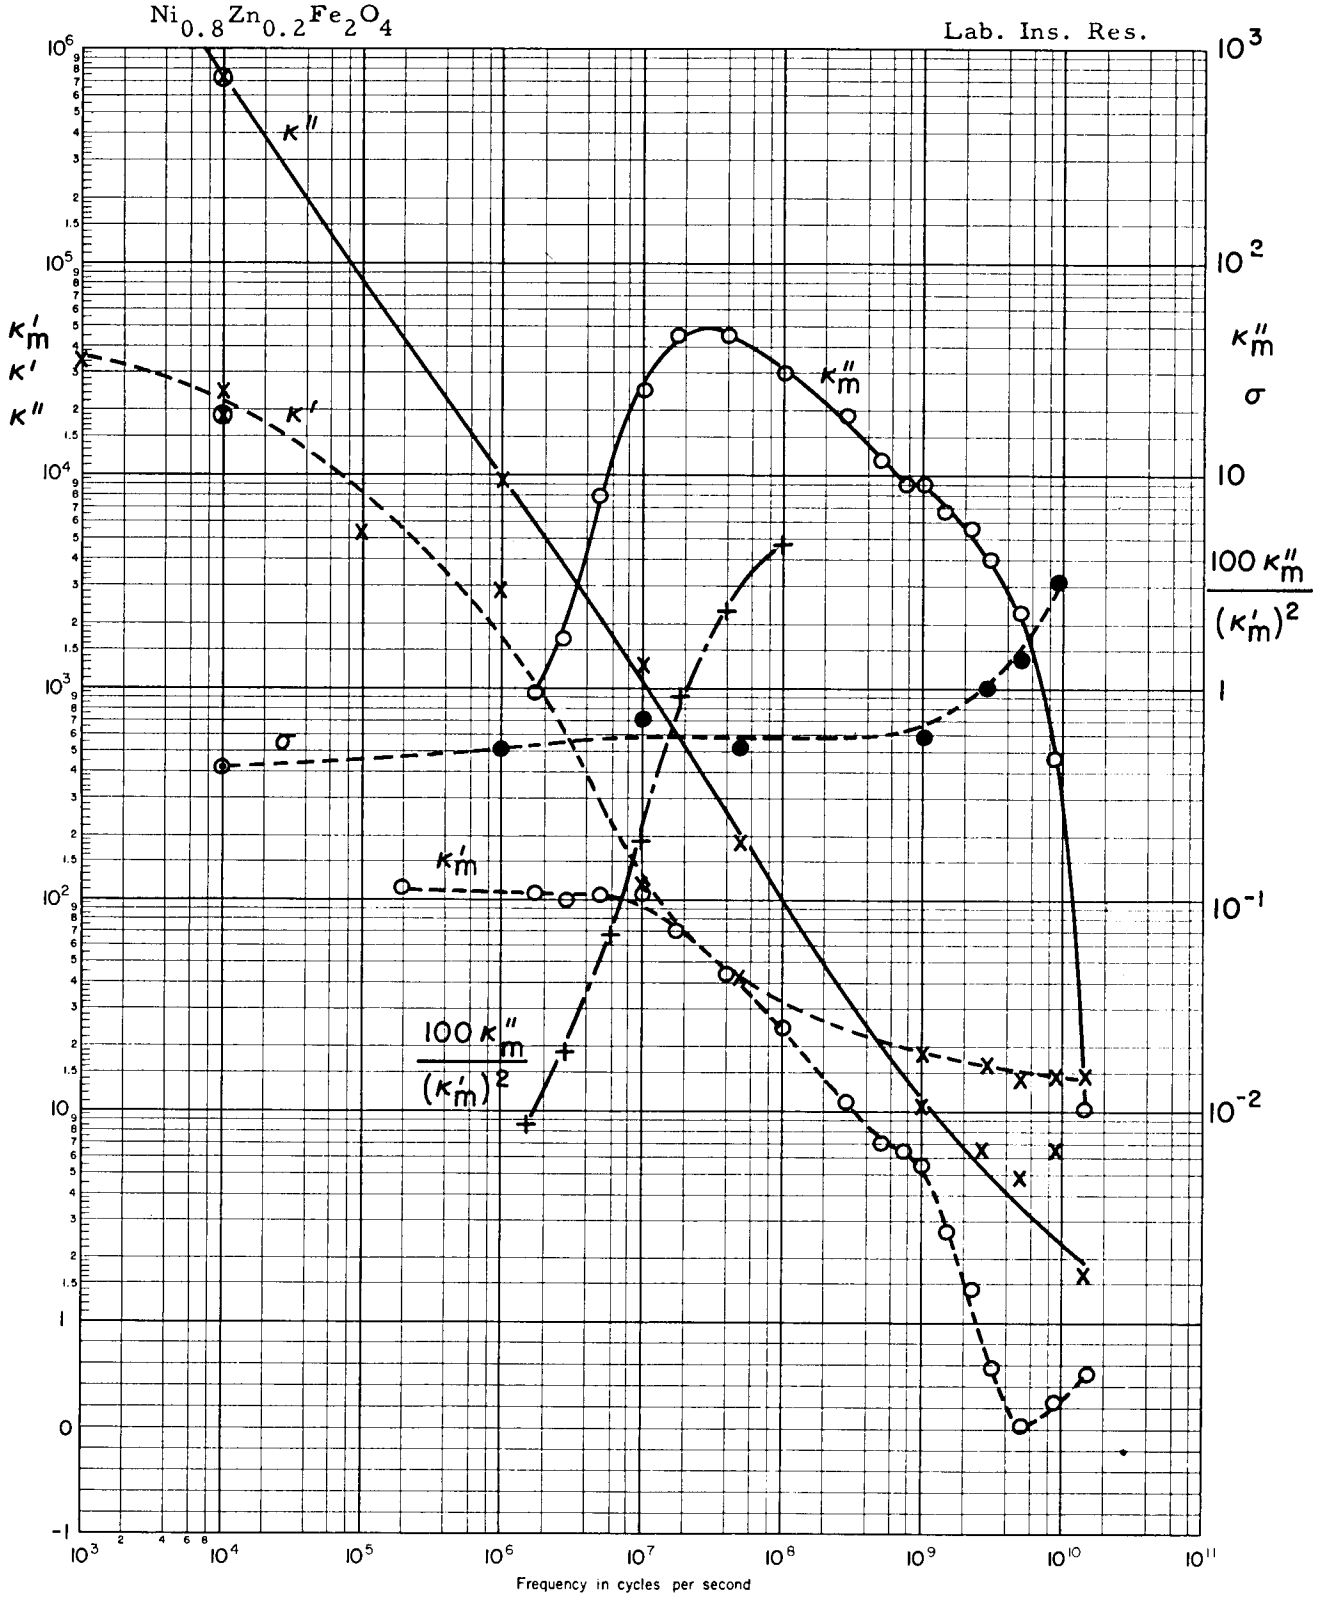


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

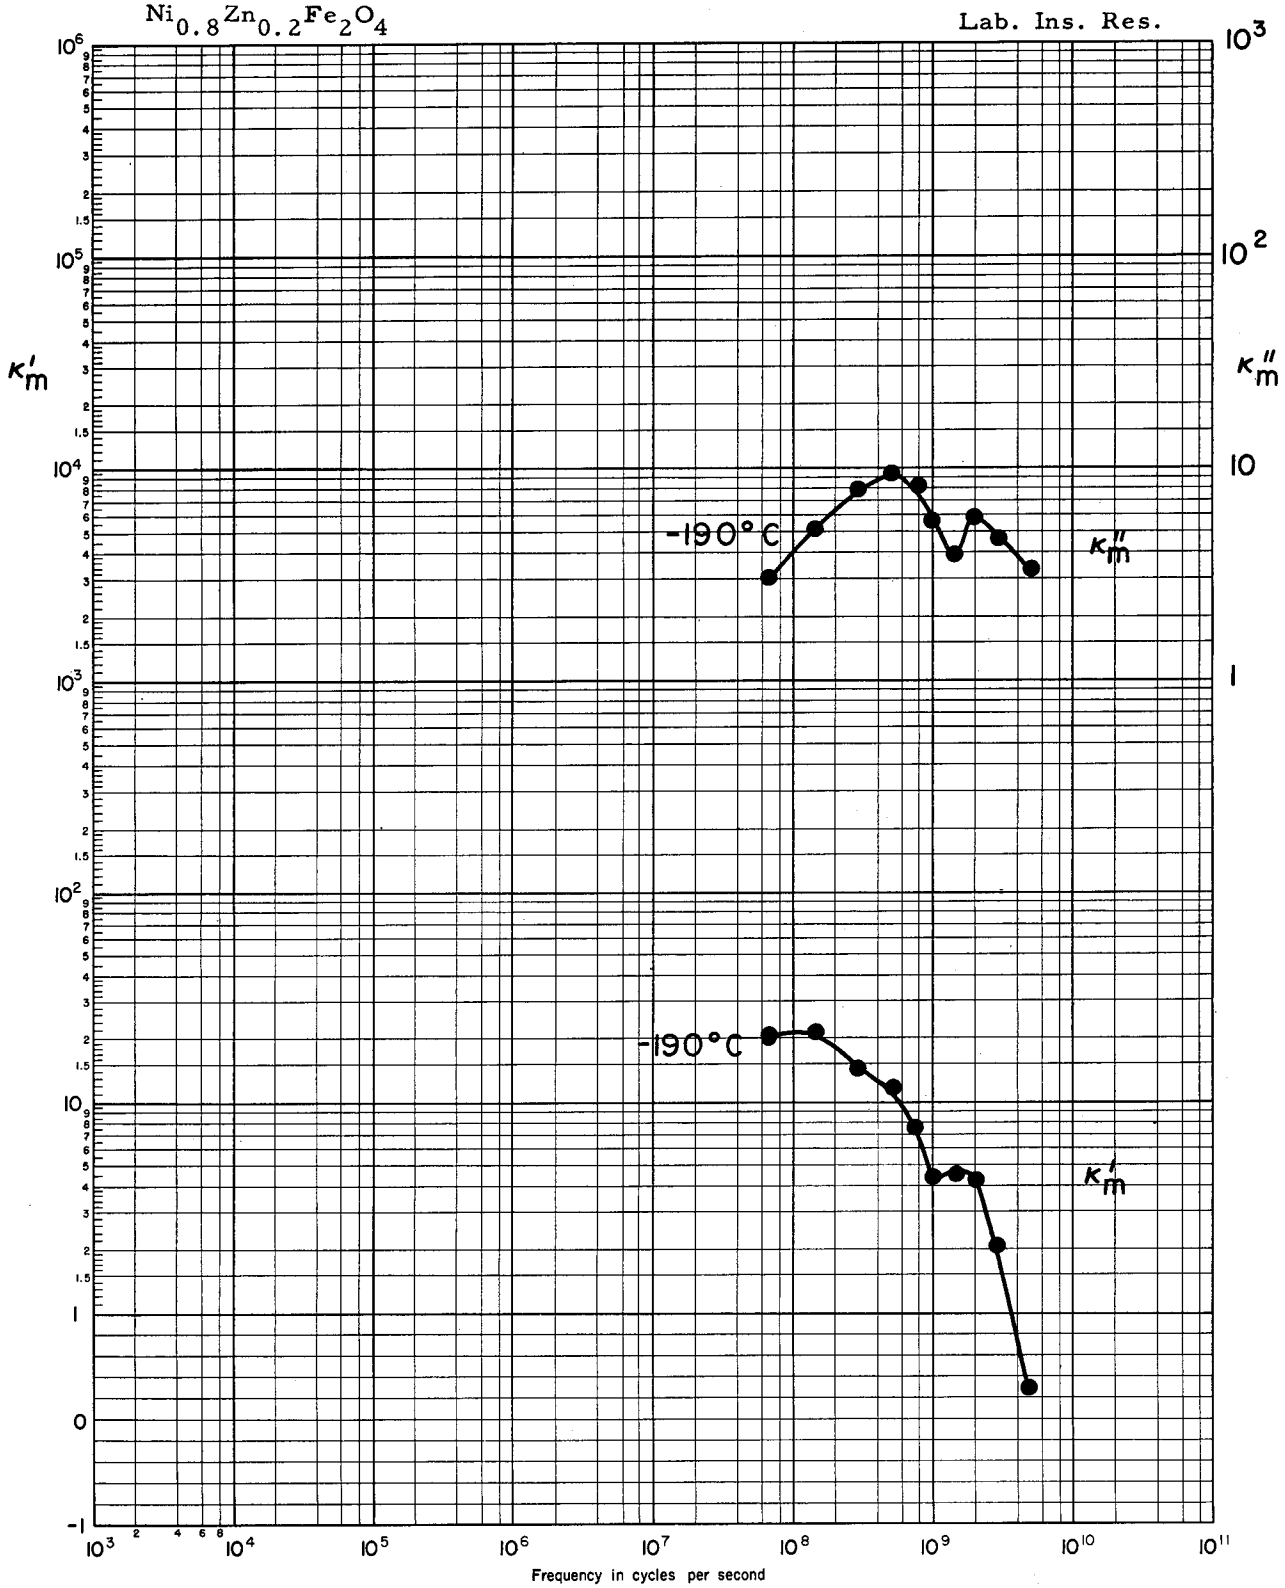


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

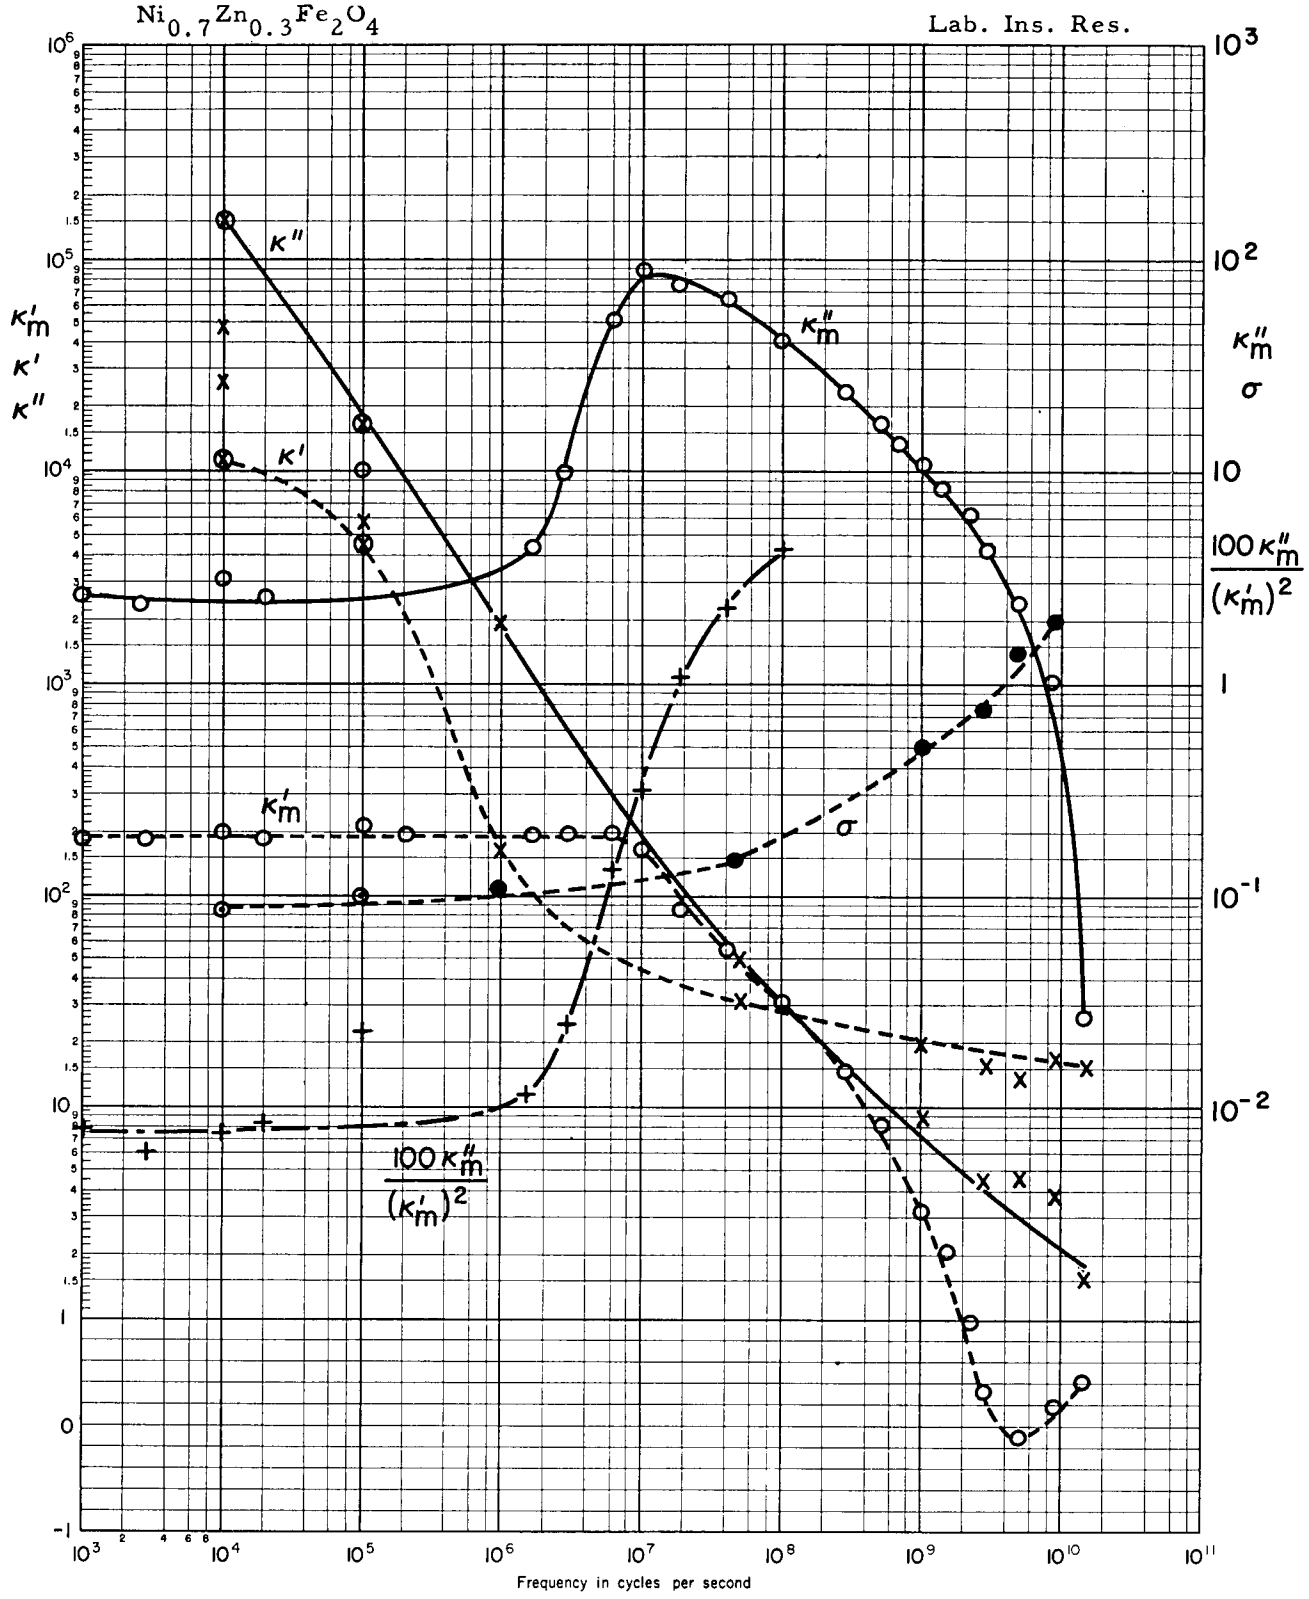


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

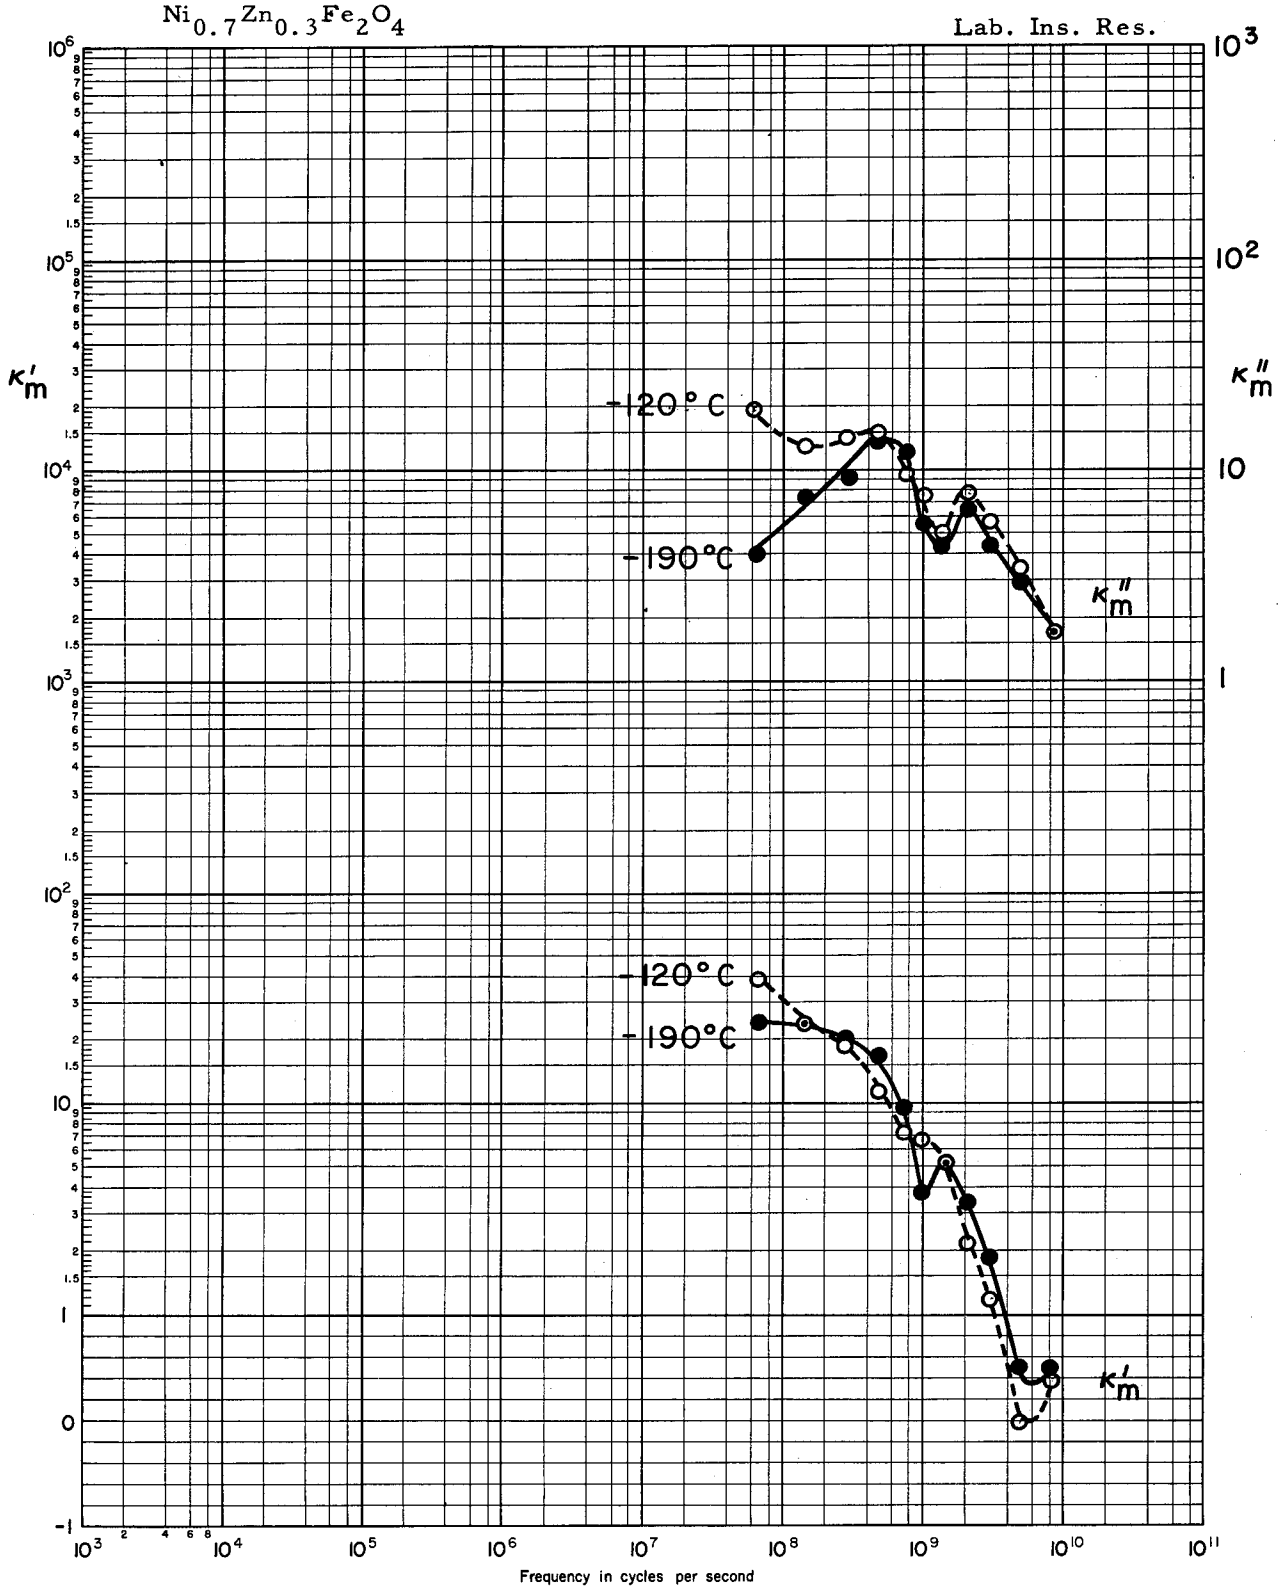

IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

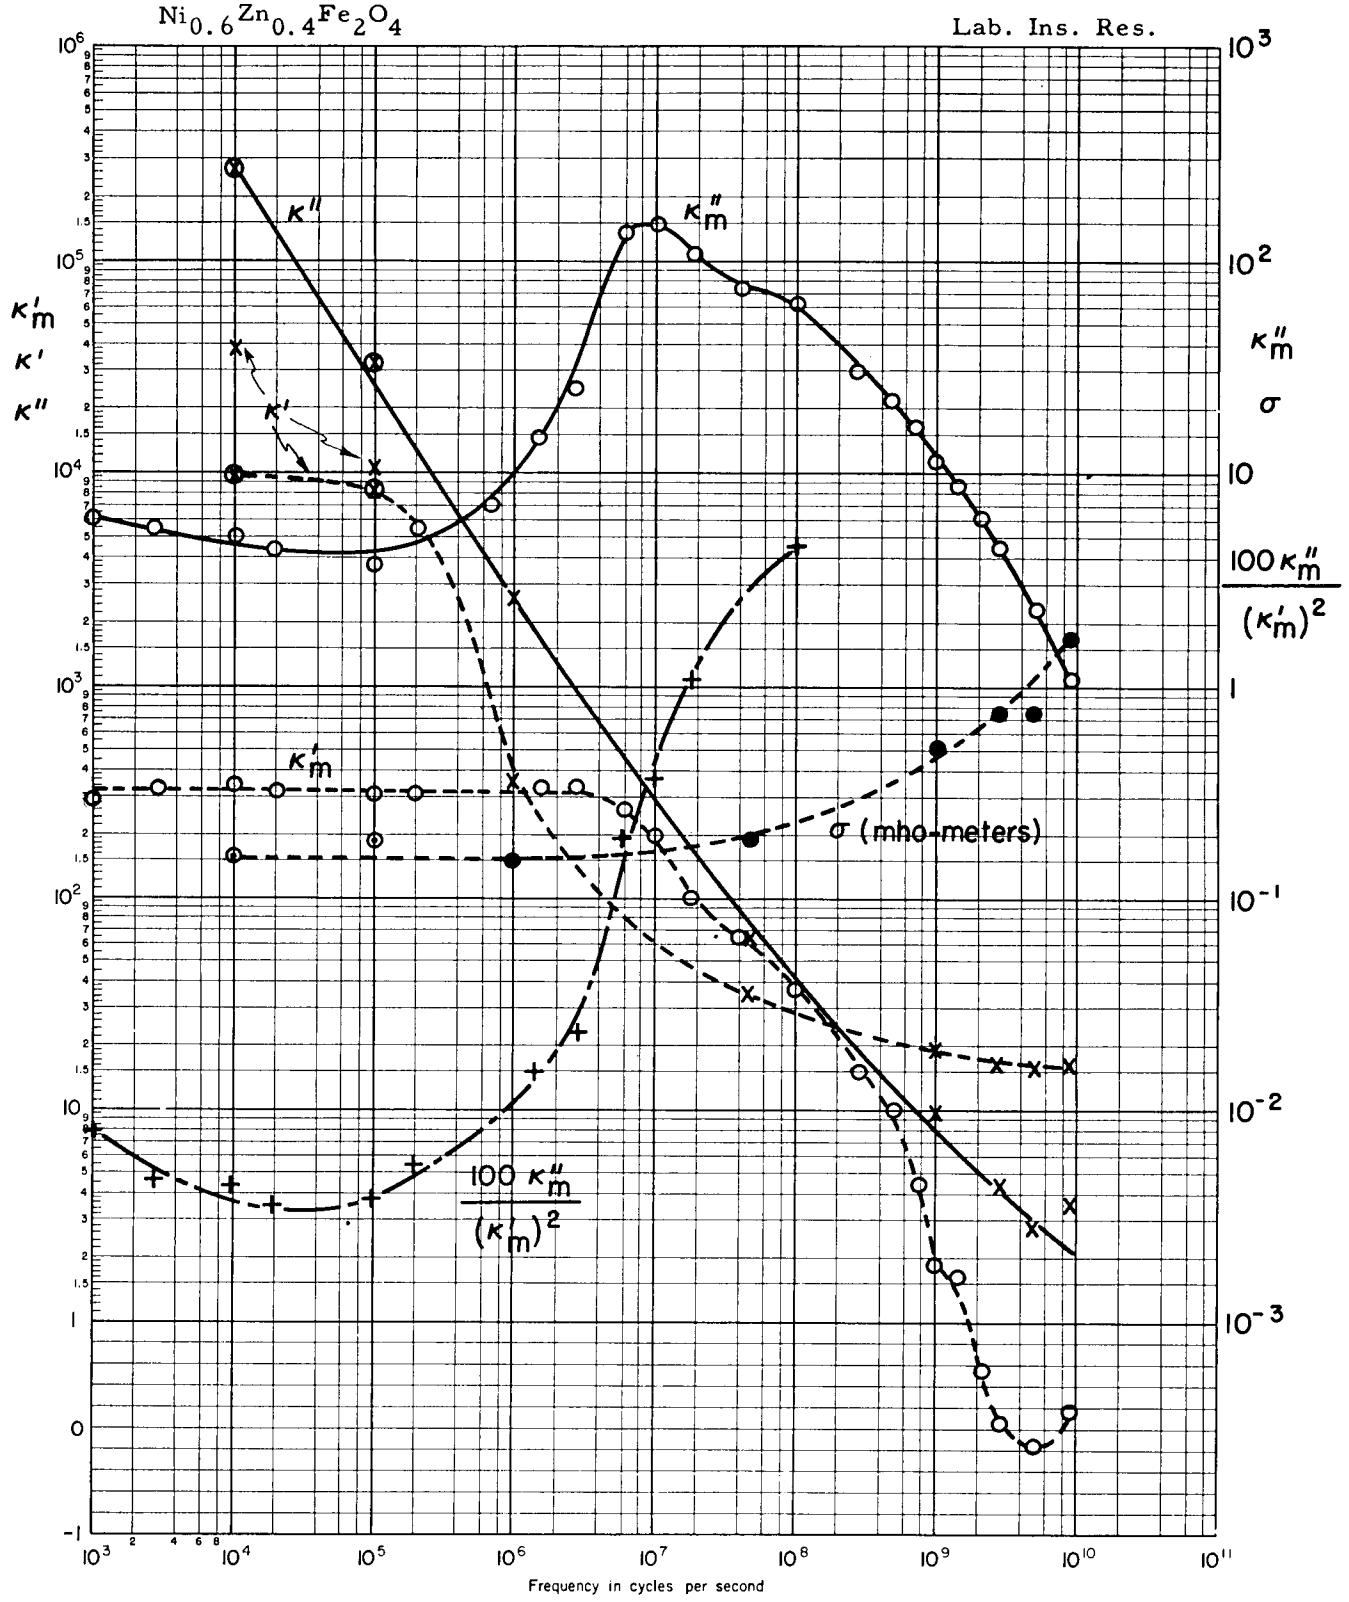


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

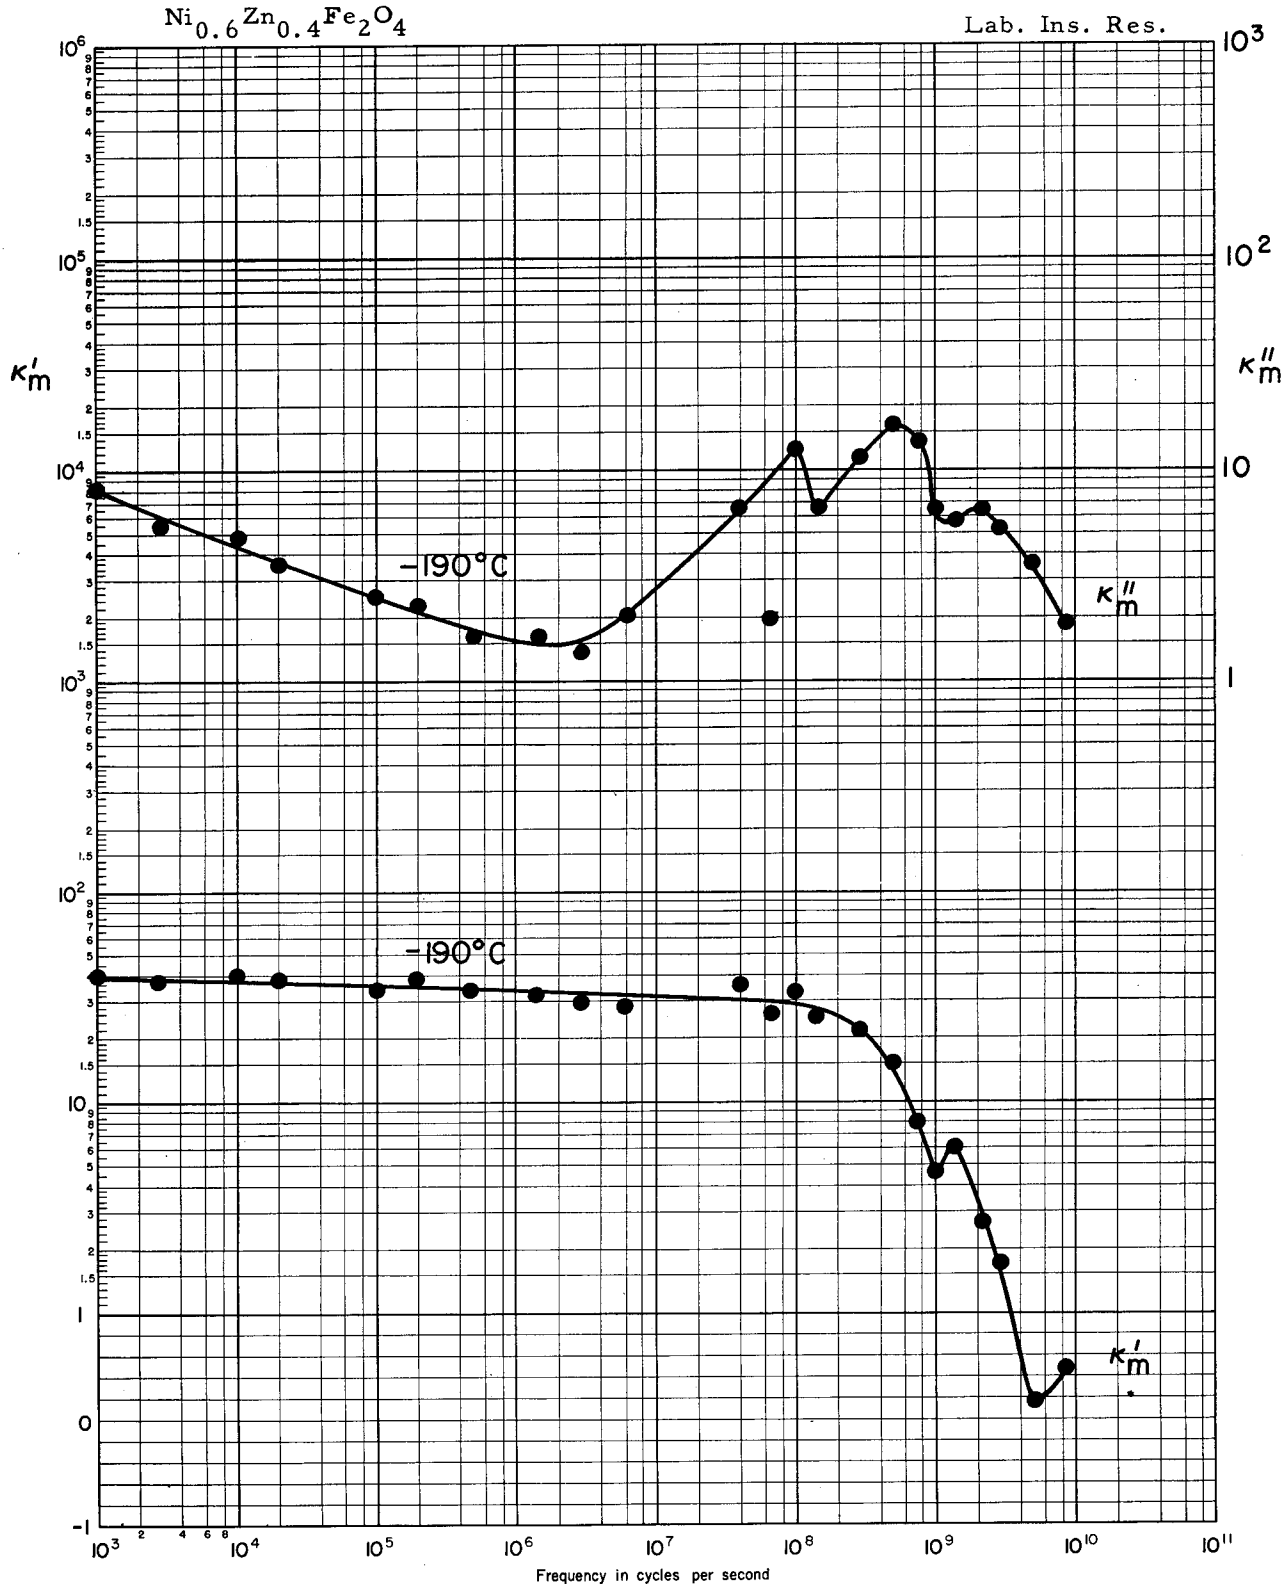


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

$Ni_{0.5}Zn_{0.5}Fe_2O_4$

Lab. Ins. Res.

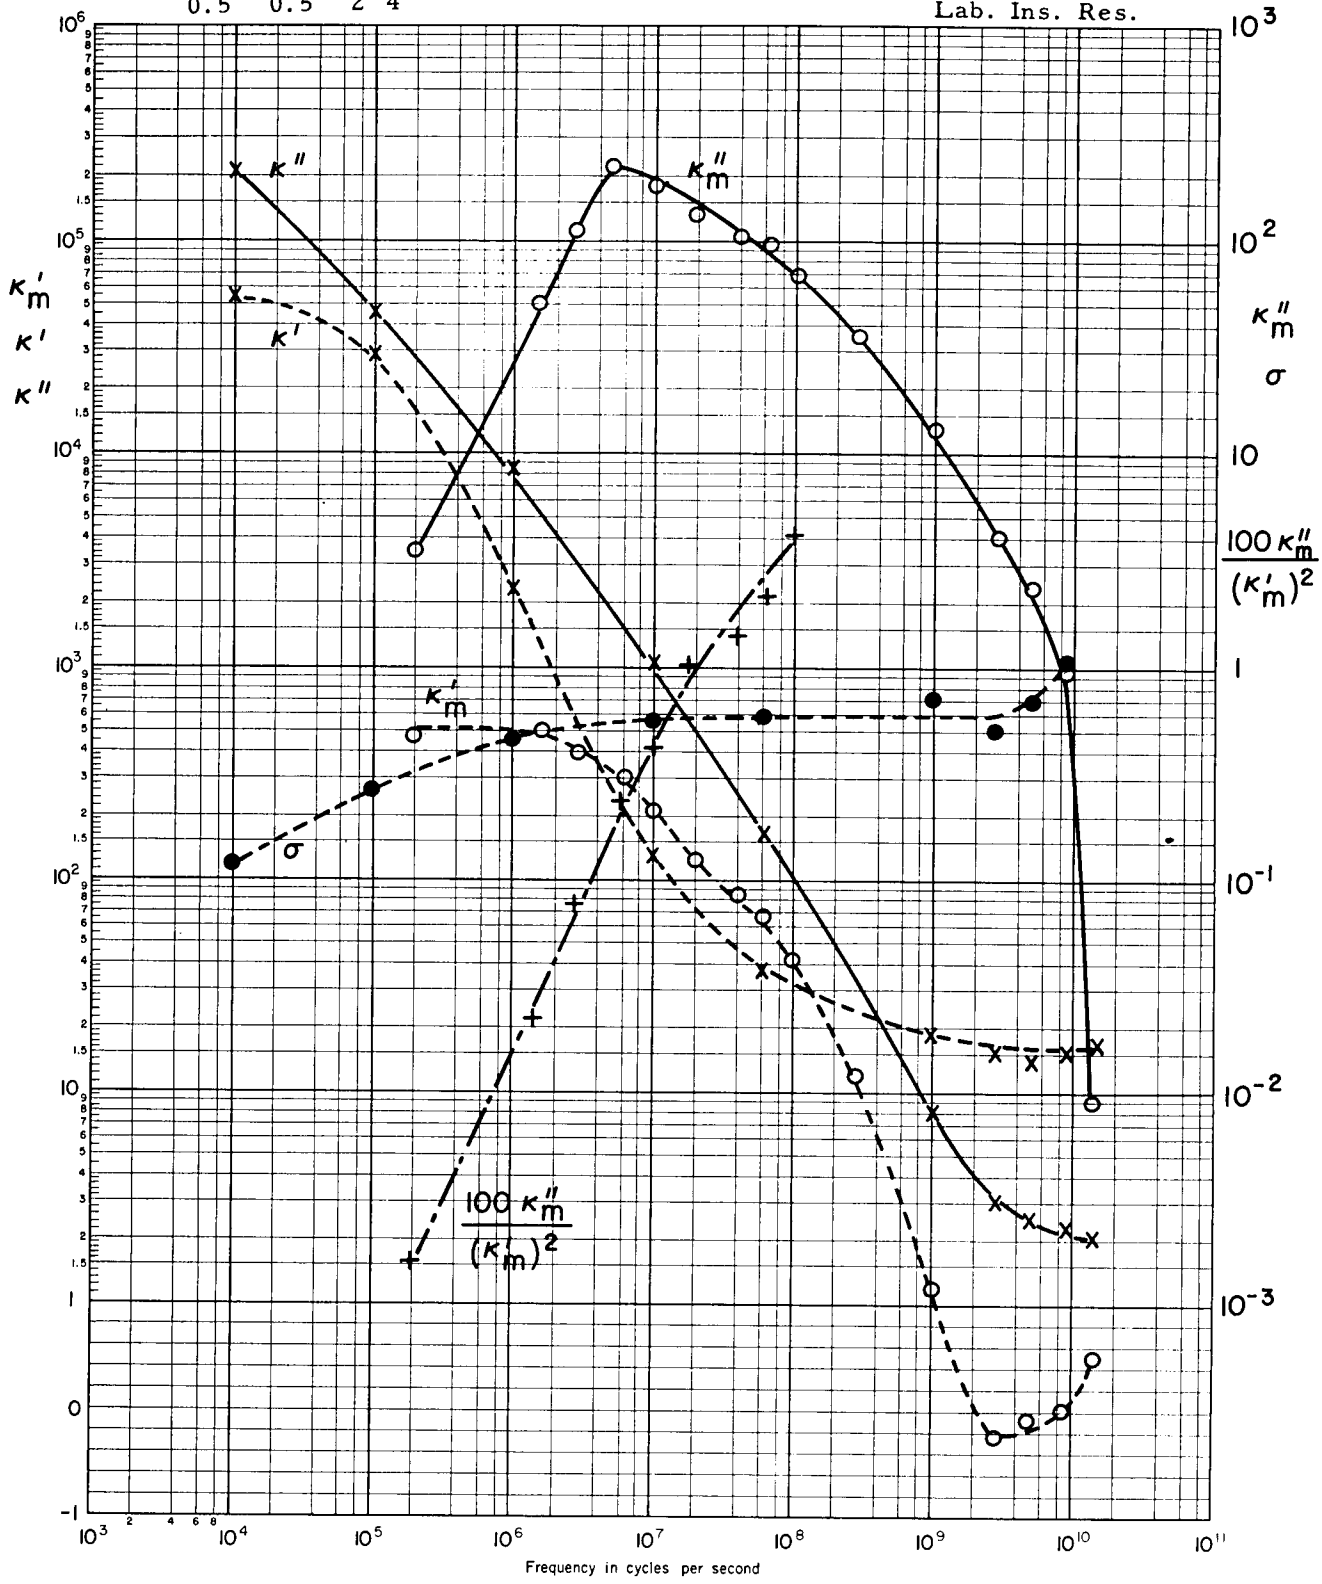


IV A.8. Nickel-Zinc Ferrites, High Density Ceramics

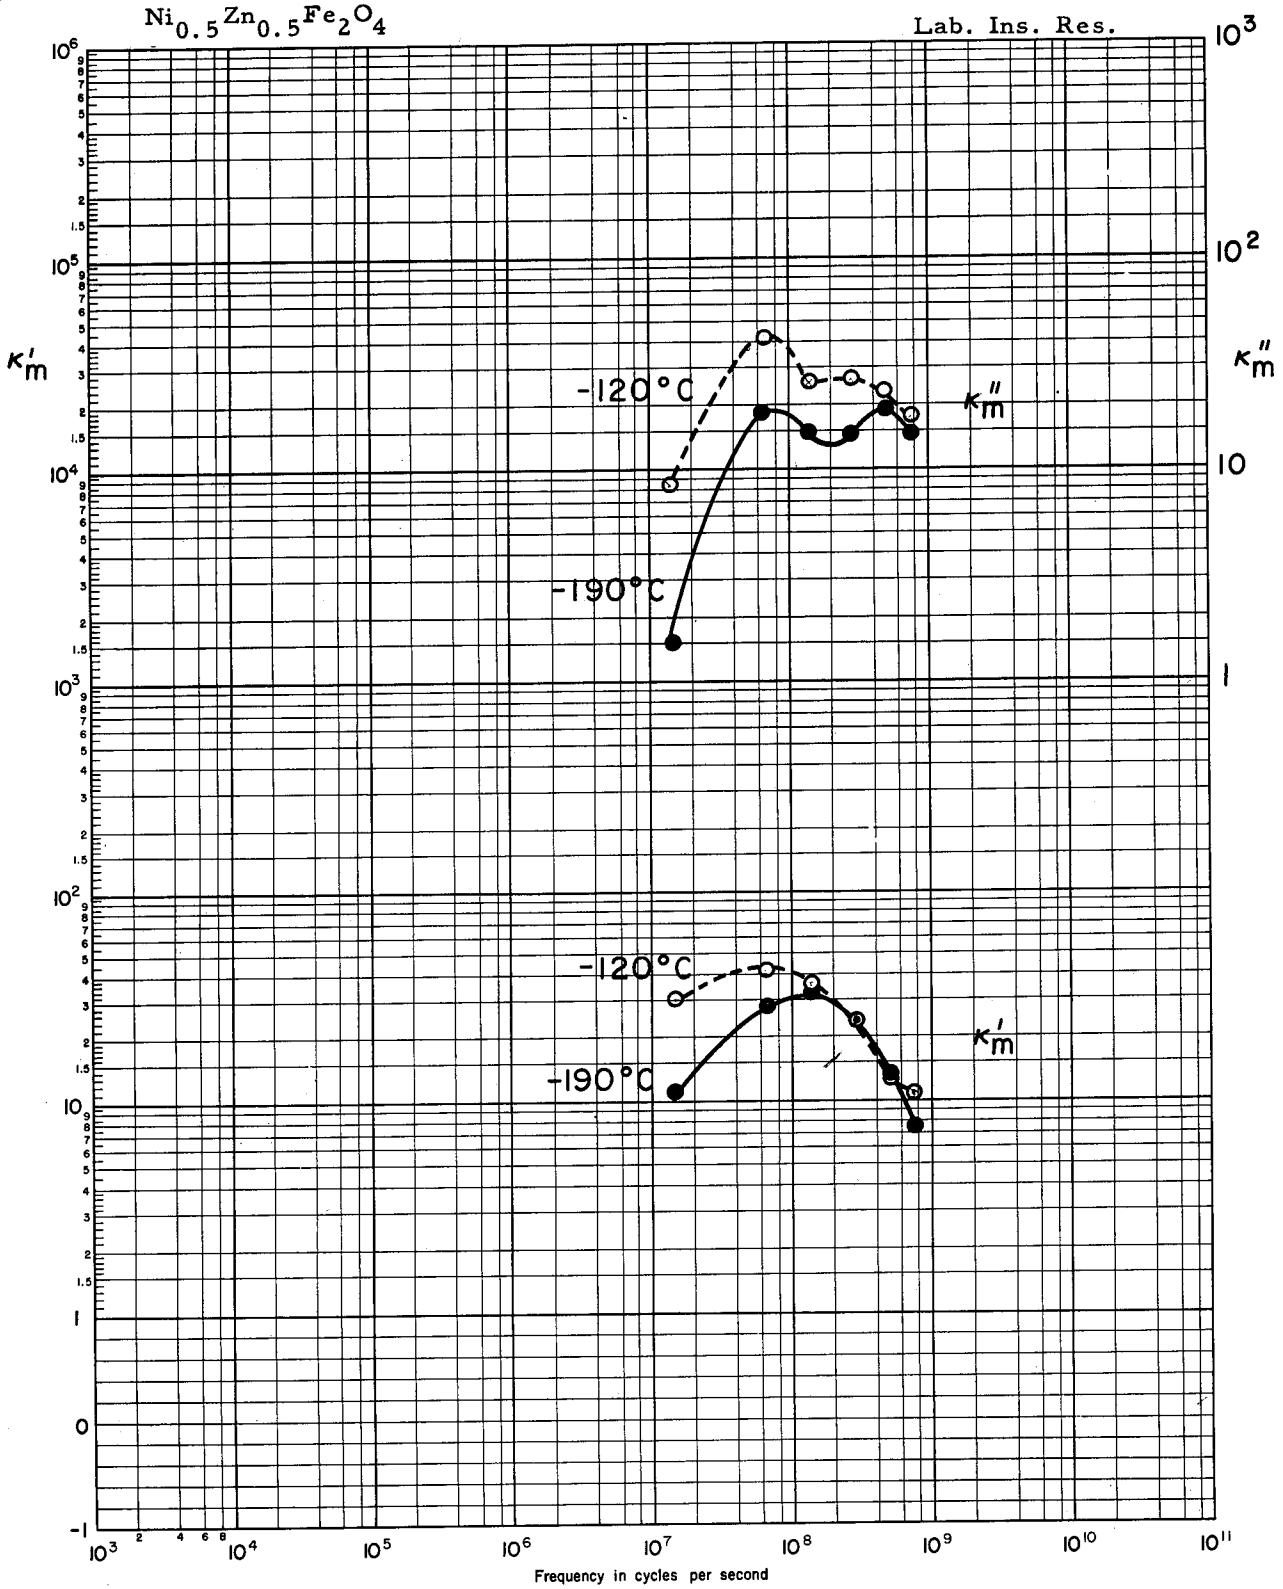


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

$Ni_{0.4}Zn_{0.6}Fe_2O_4$


Lab. Ins. Res.

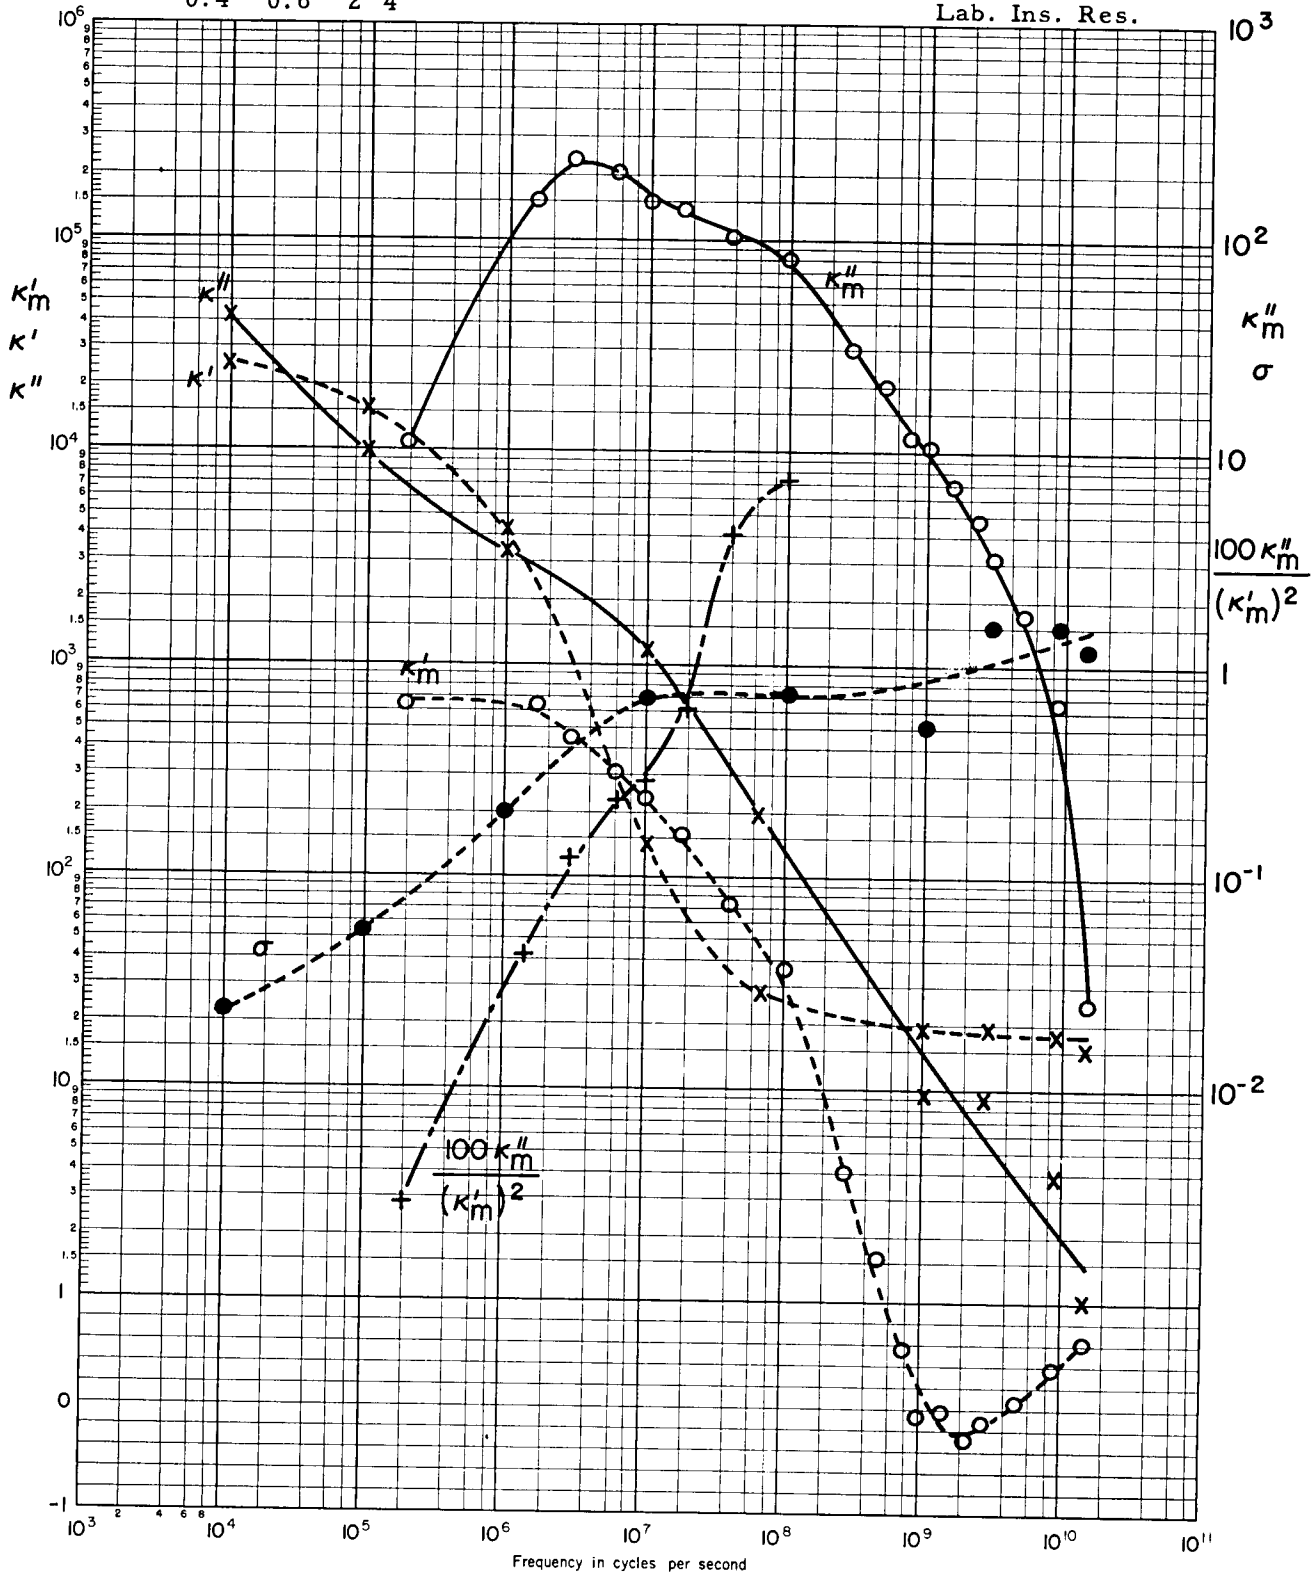


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

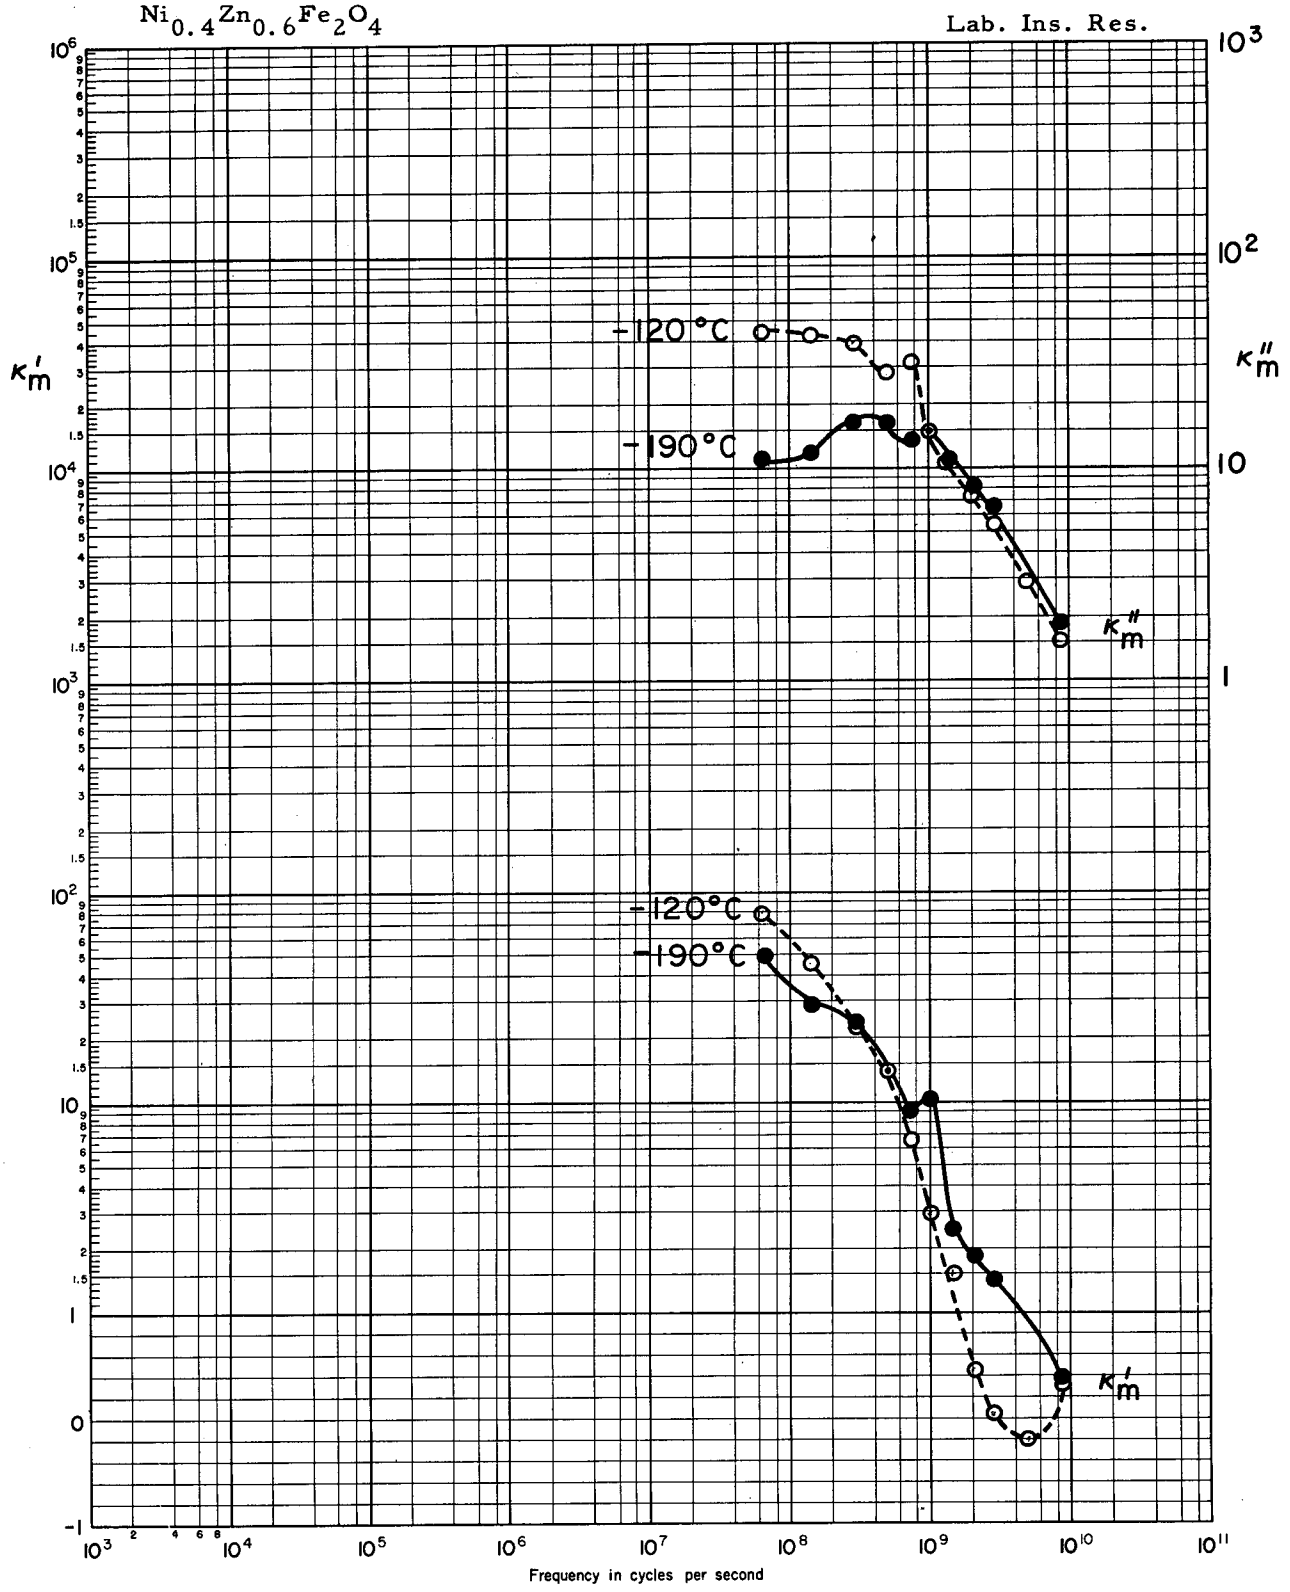


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

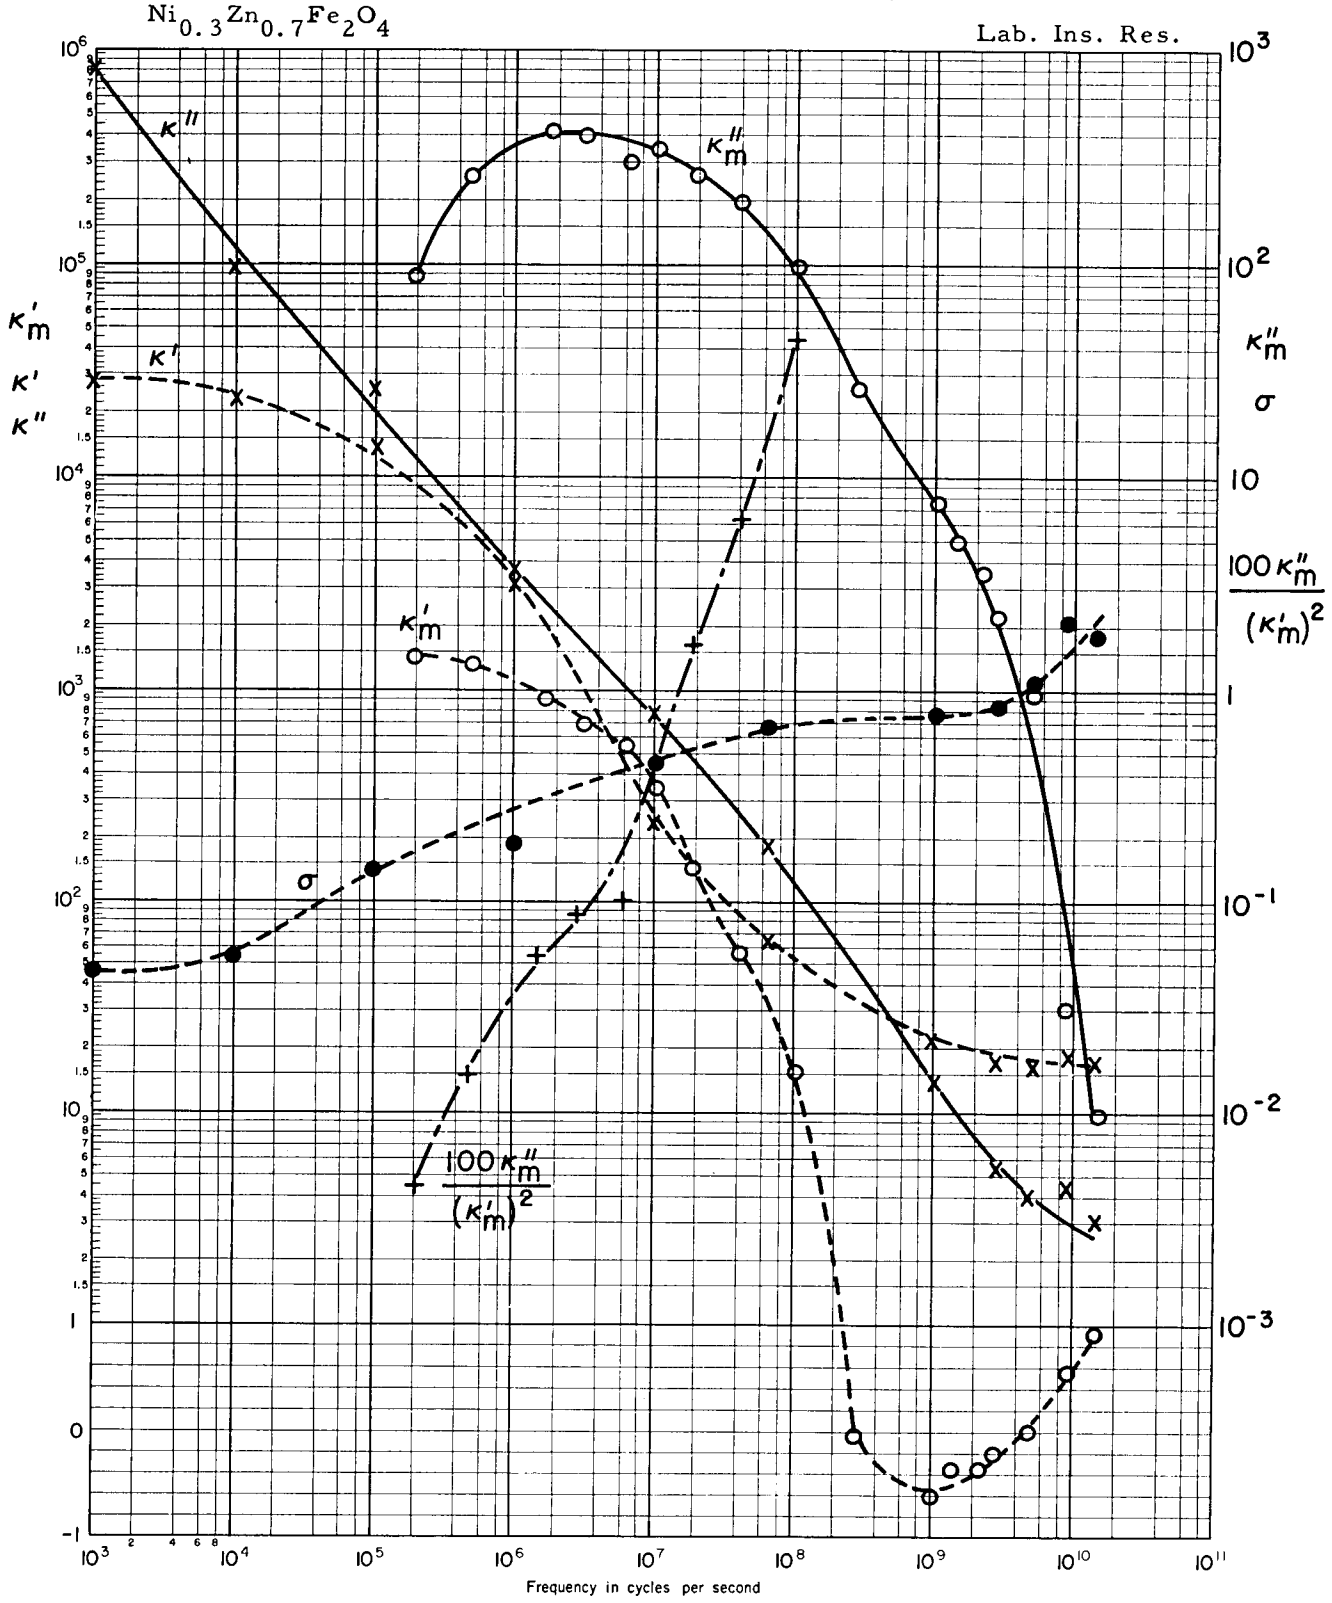


IV A 8. Nickel-Zinc Ferrites, High Density Ceramics

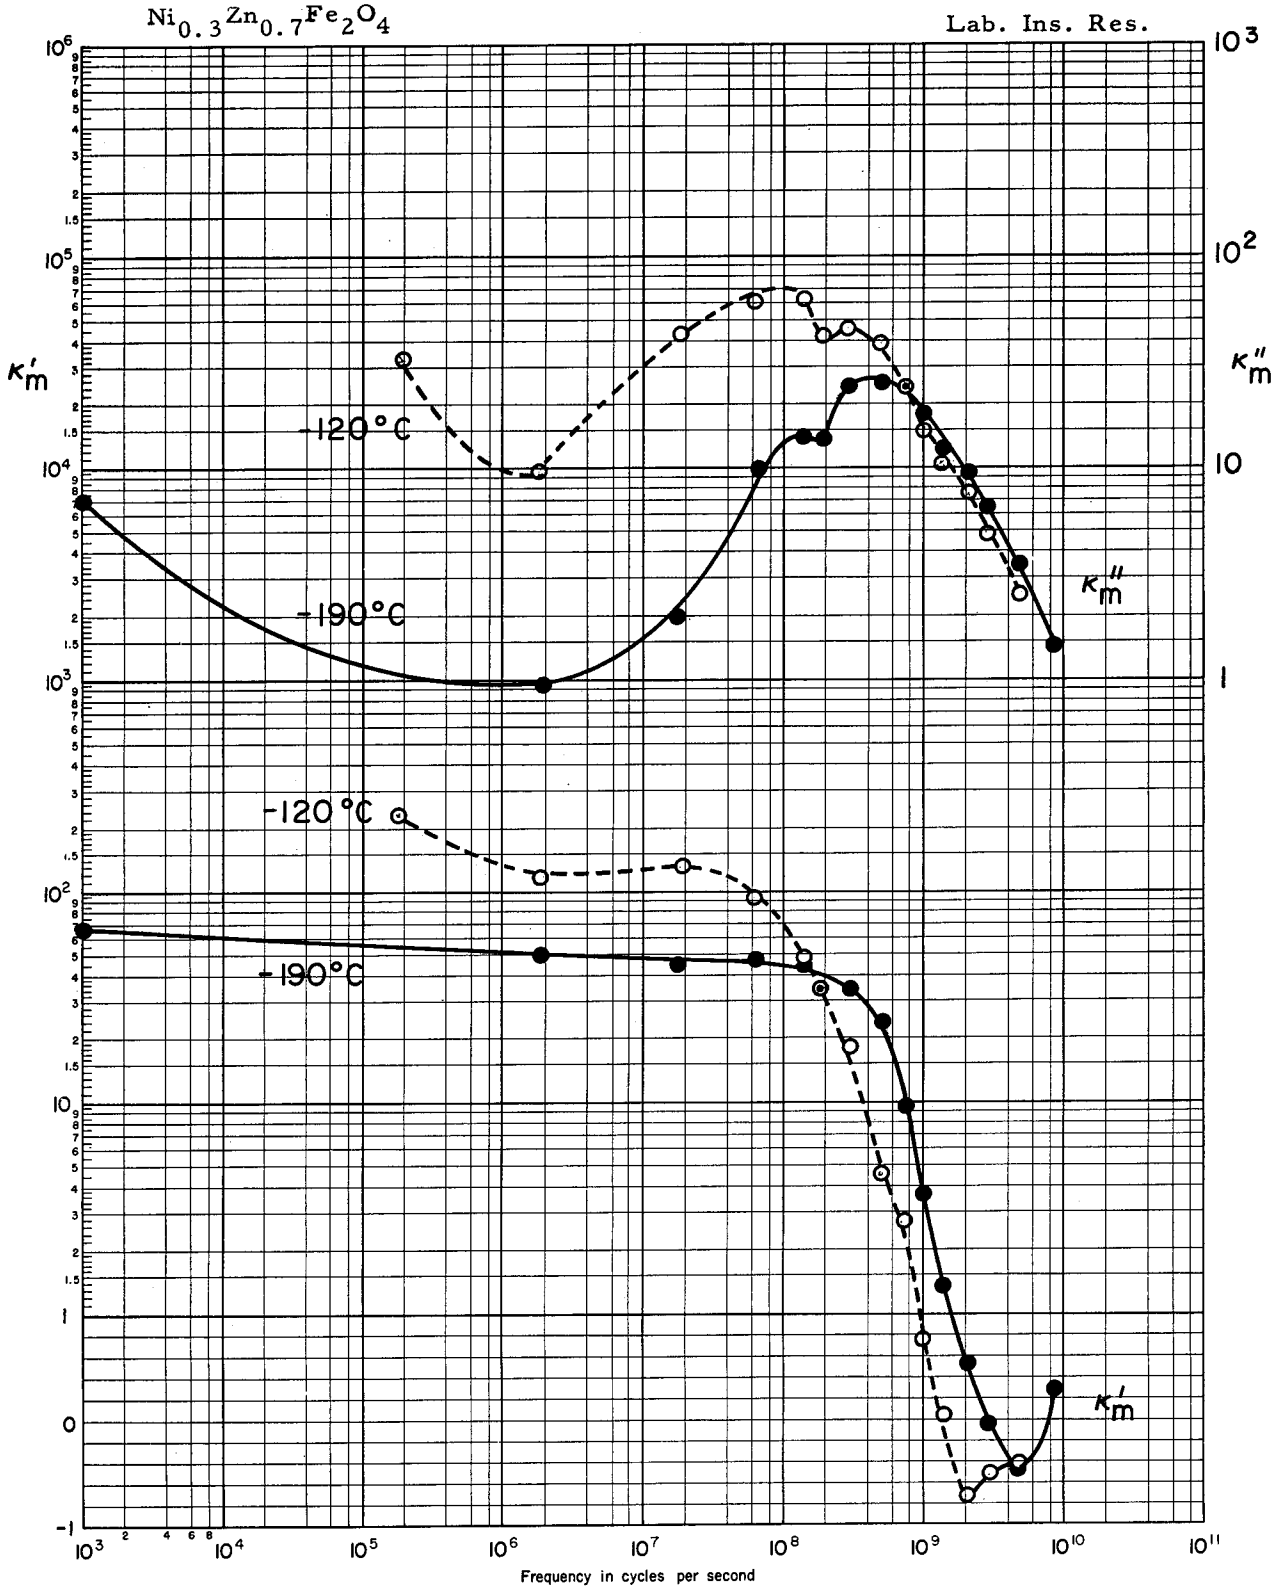


IV A 9. Zinc Ferrite, High Density Ceramic

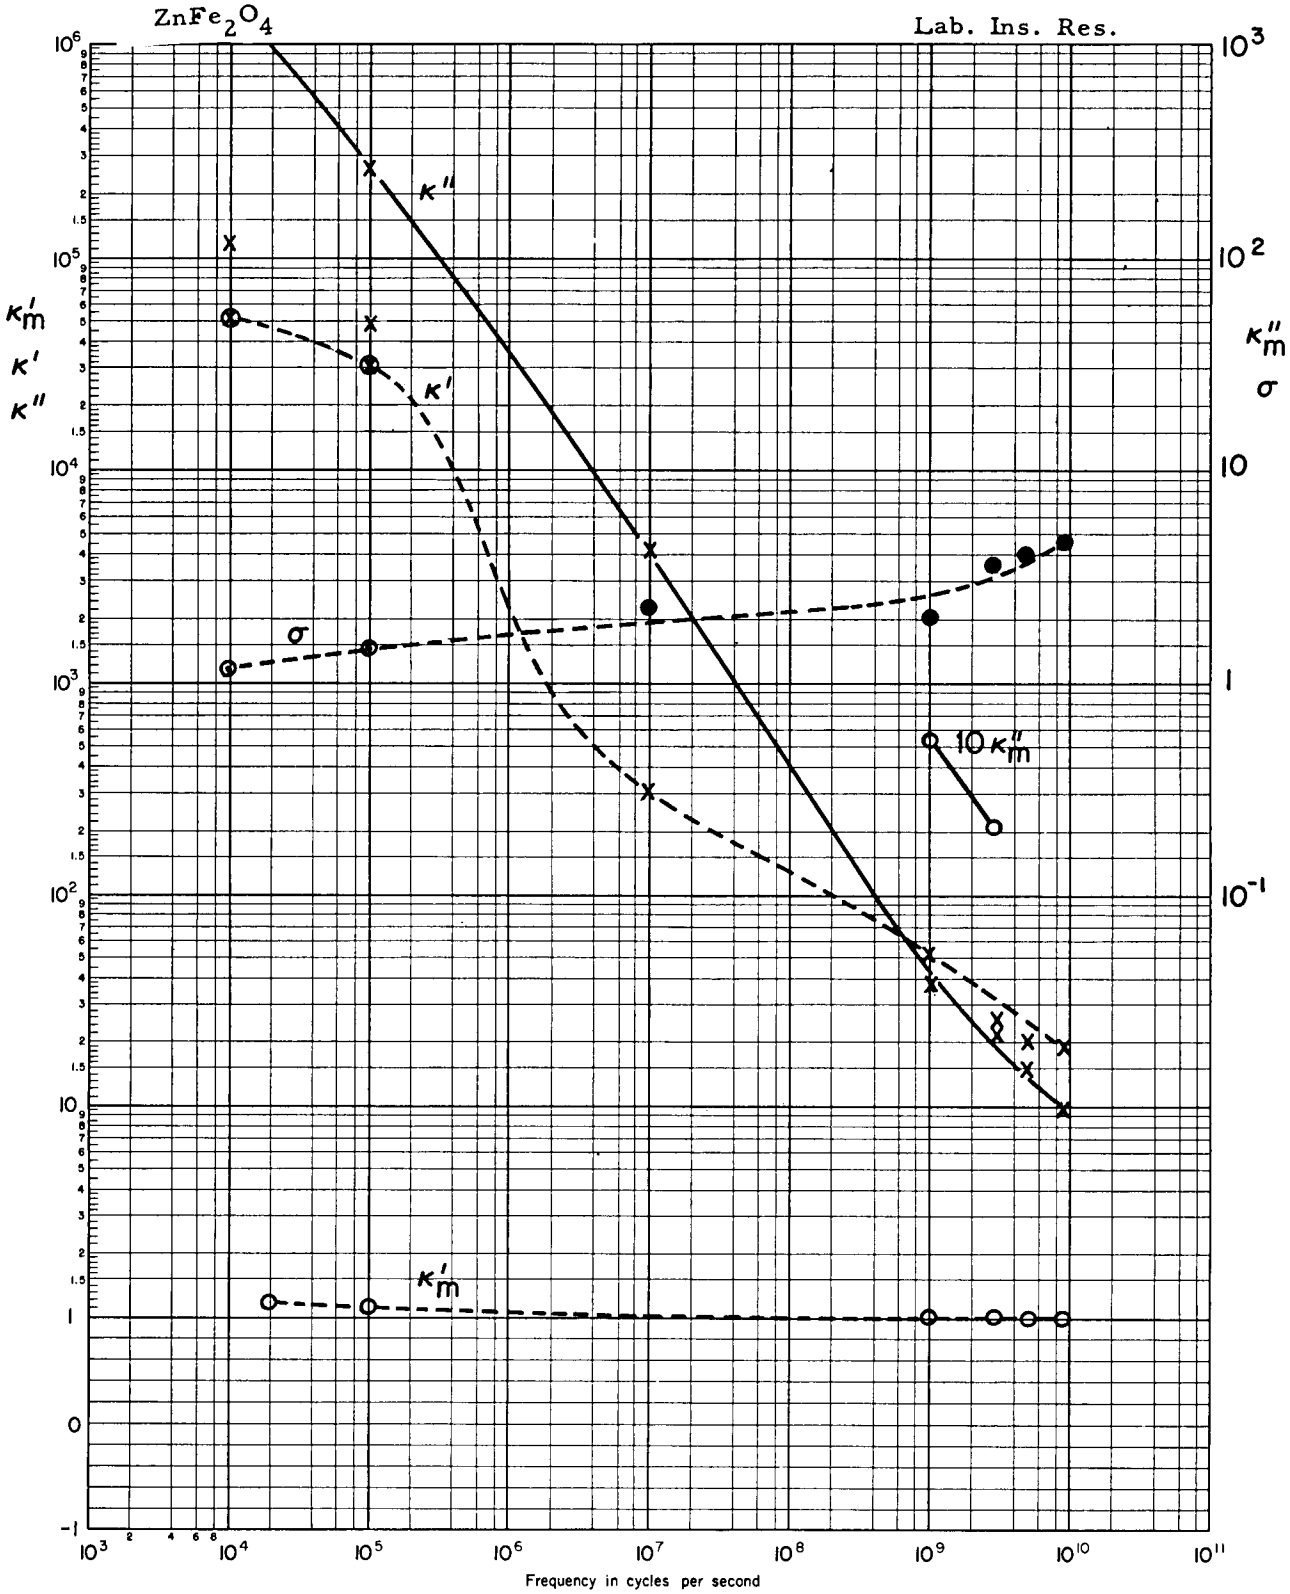


IV A 10. Commercial Ferrites

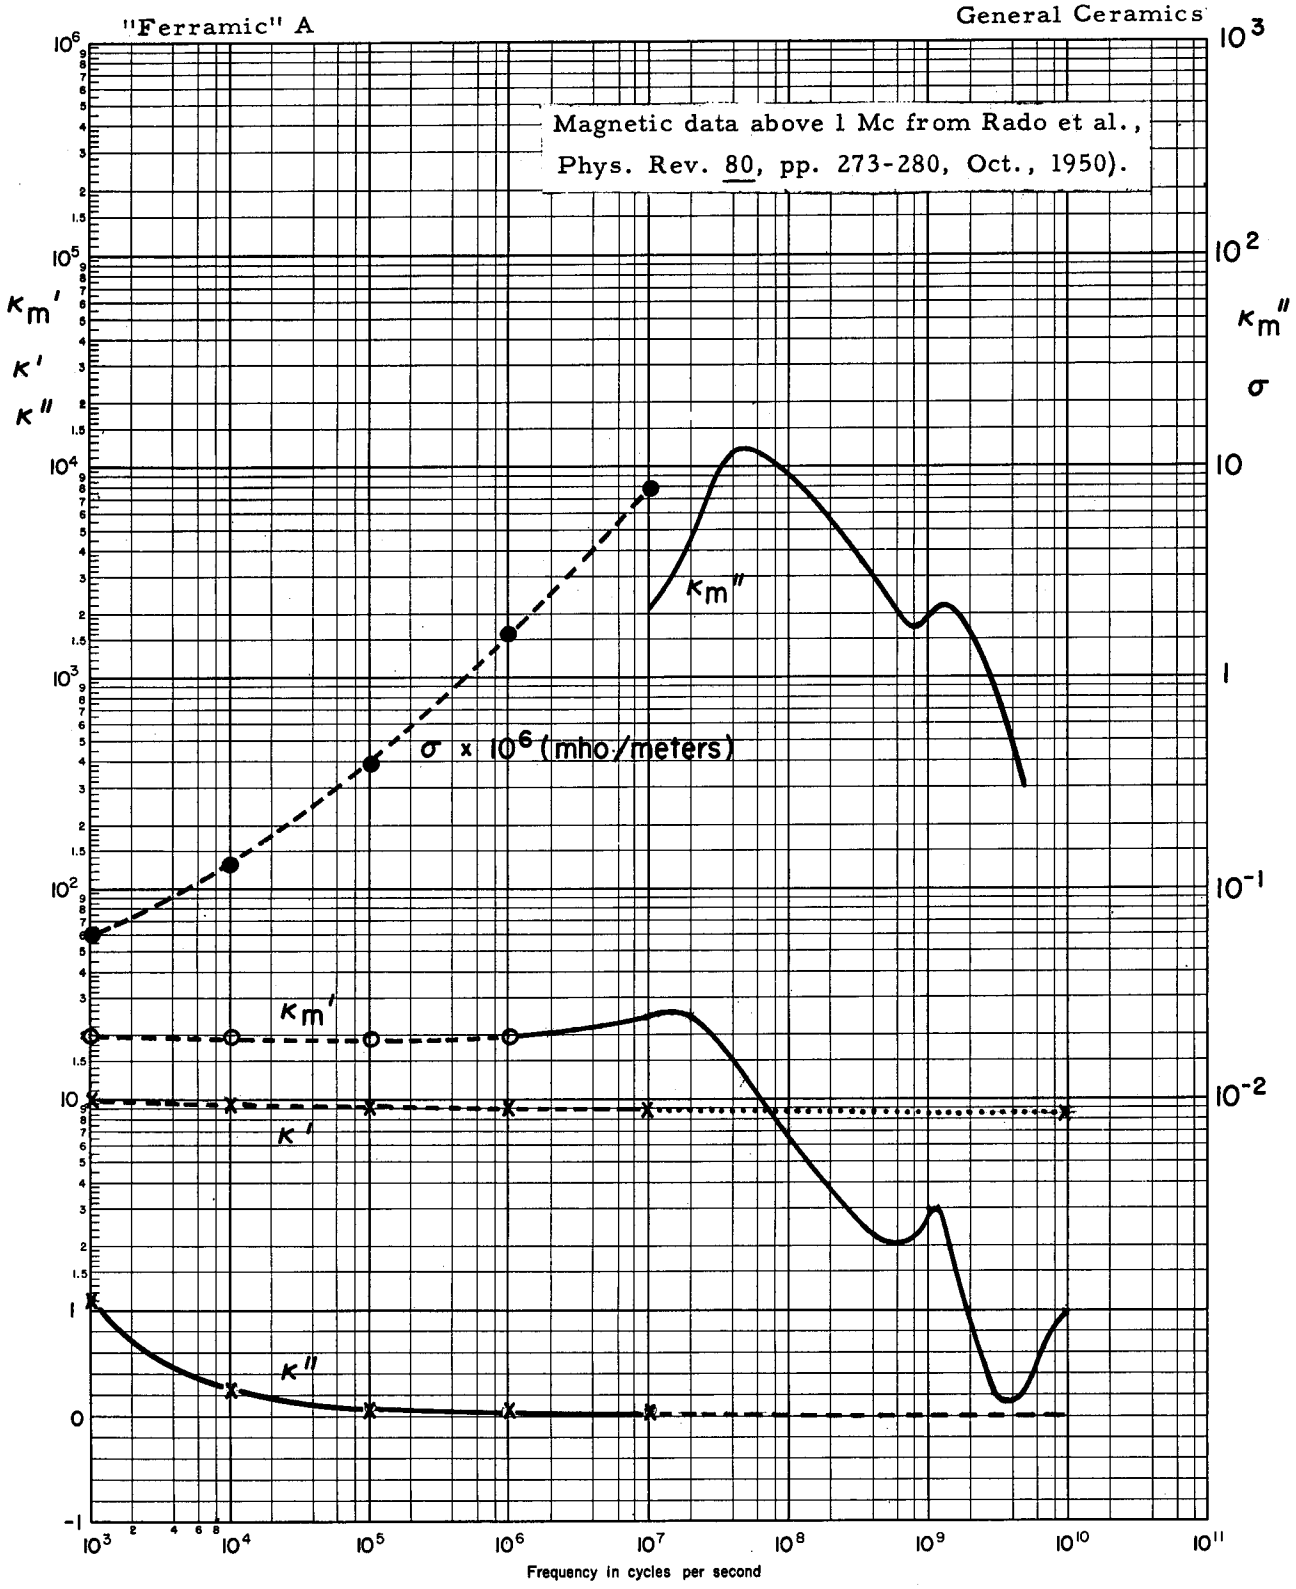


IV A 10. Commercial Ferrites

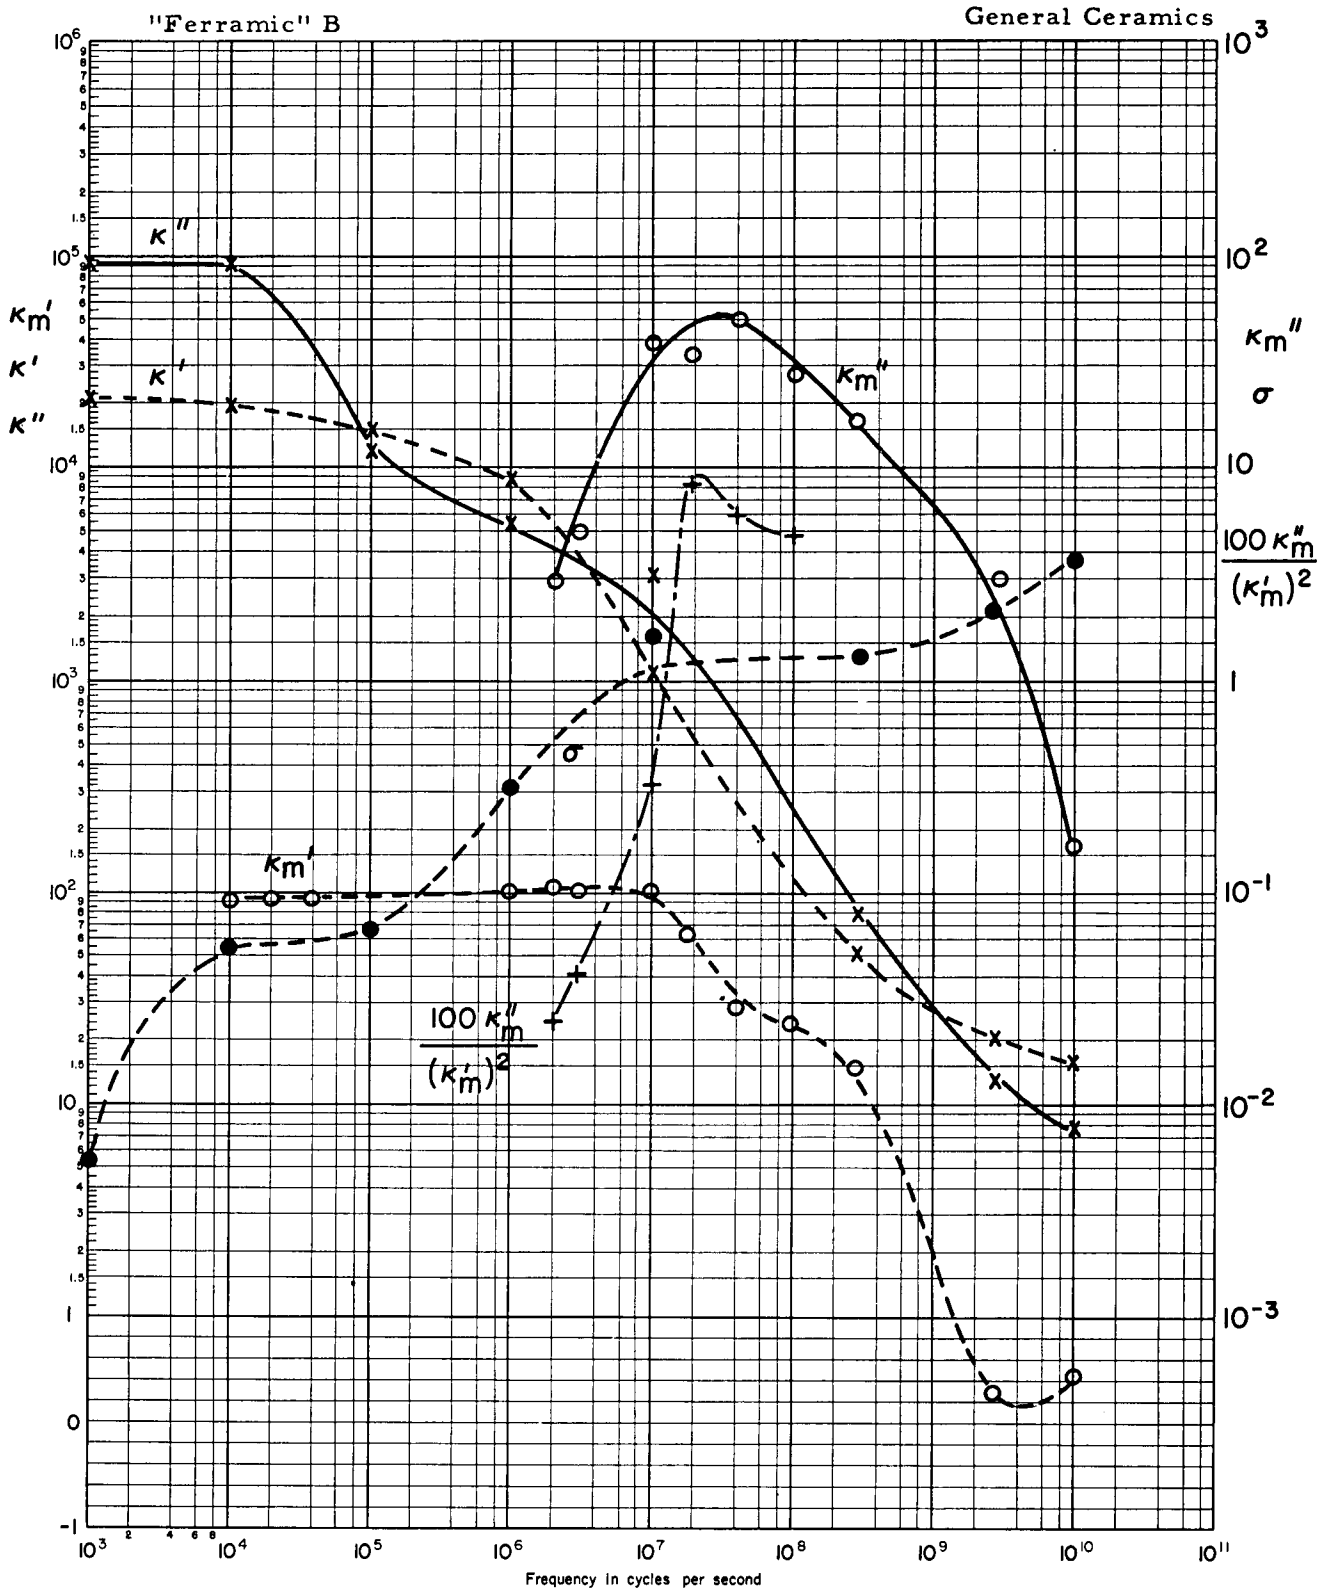

IV A 10. Commercial Ferrites

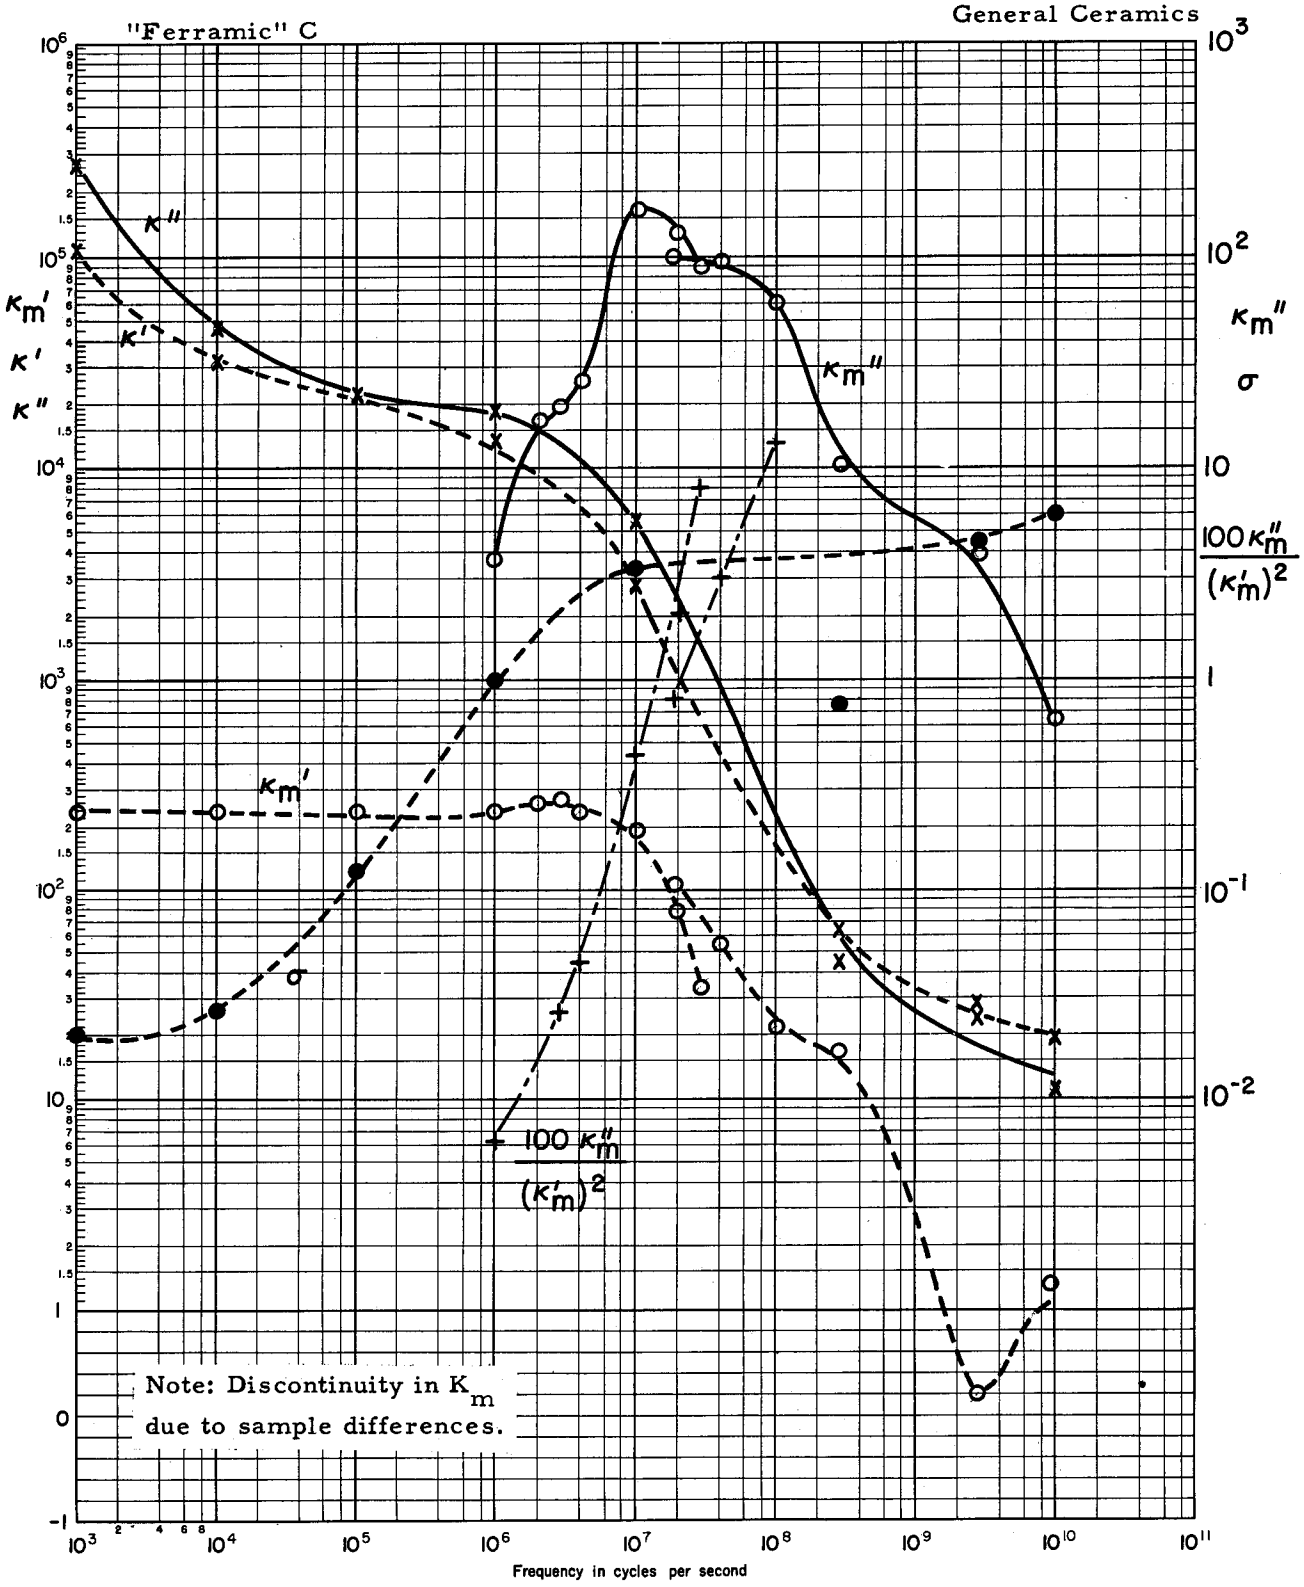


IV A 10. Commercial Ferrites

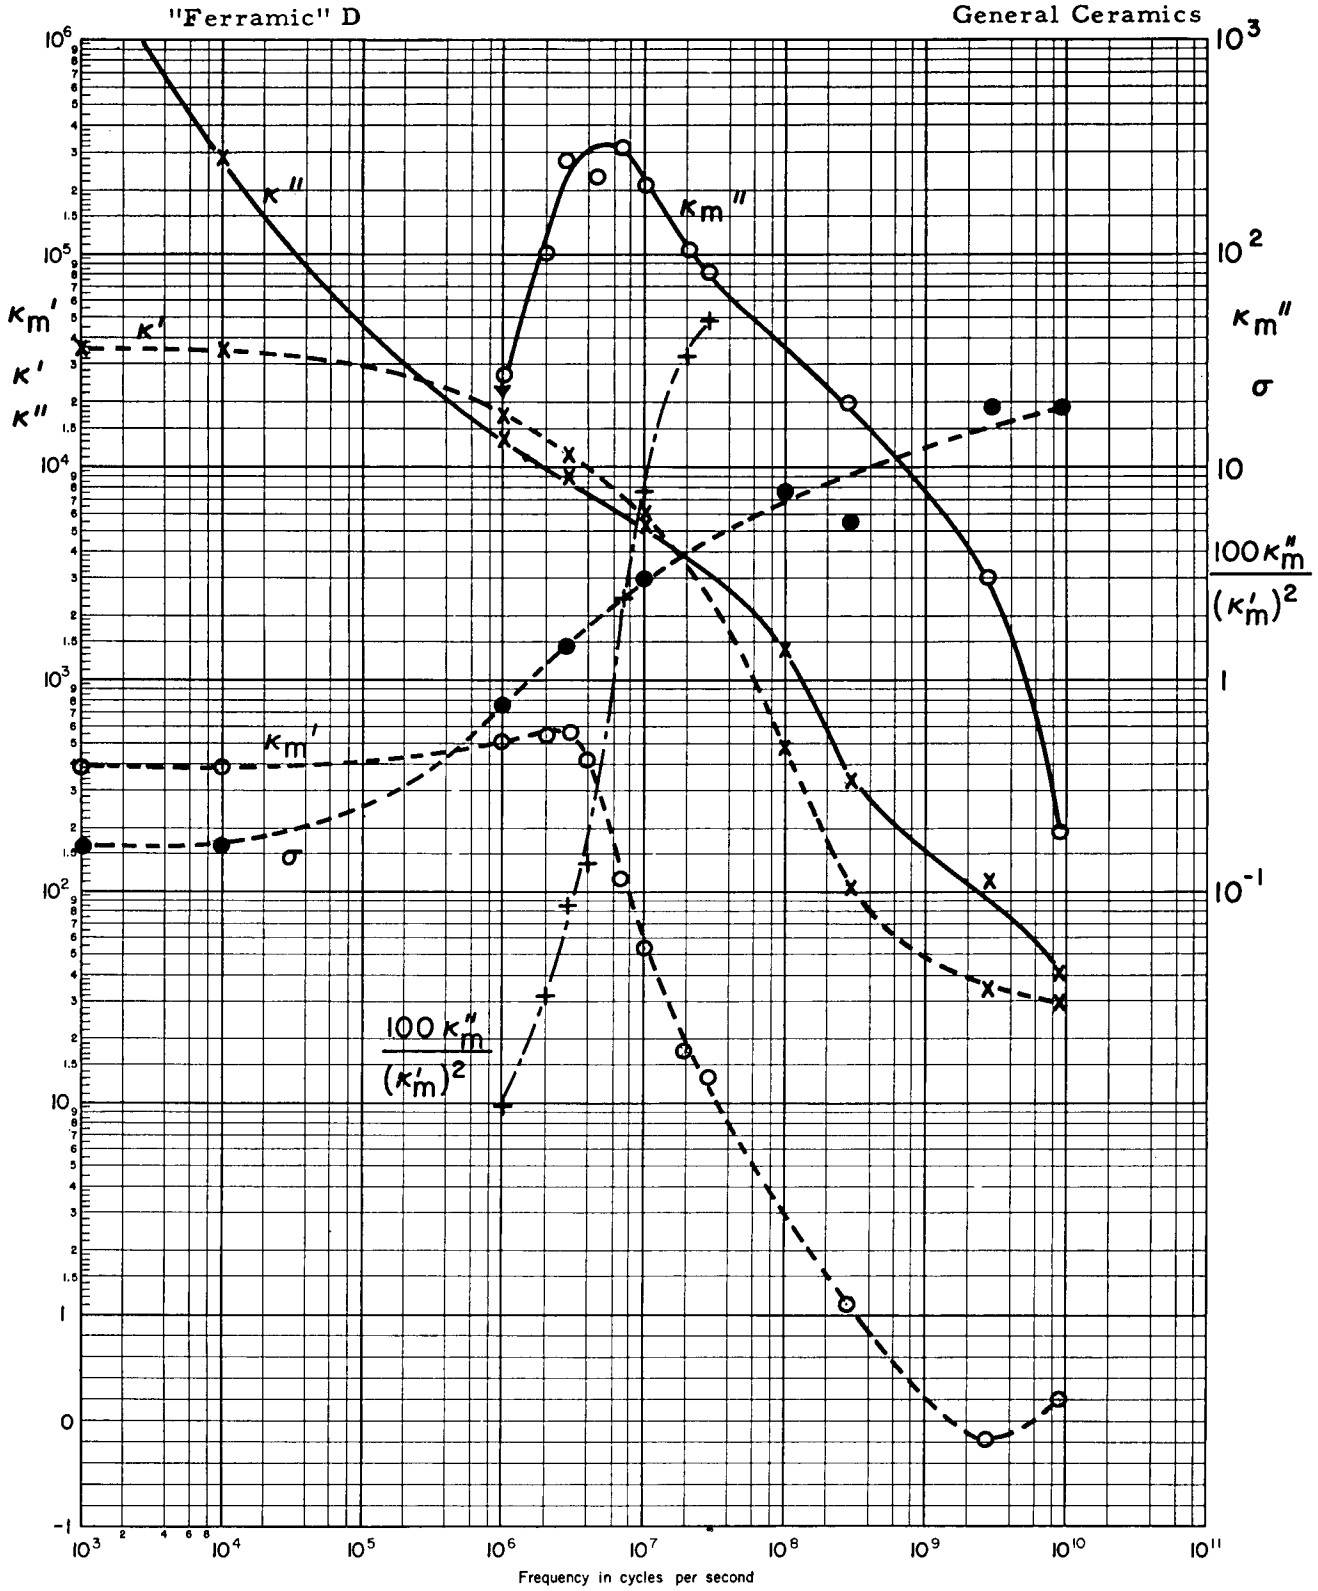


IV A 10. Commercial Ferrites


"Ferramic" E — General Ceramics

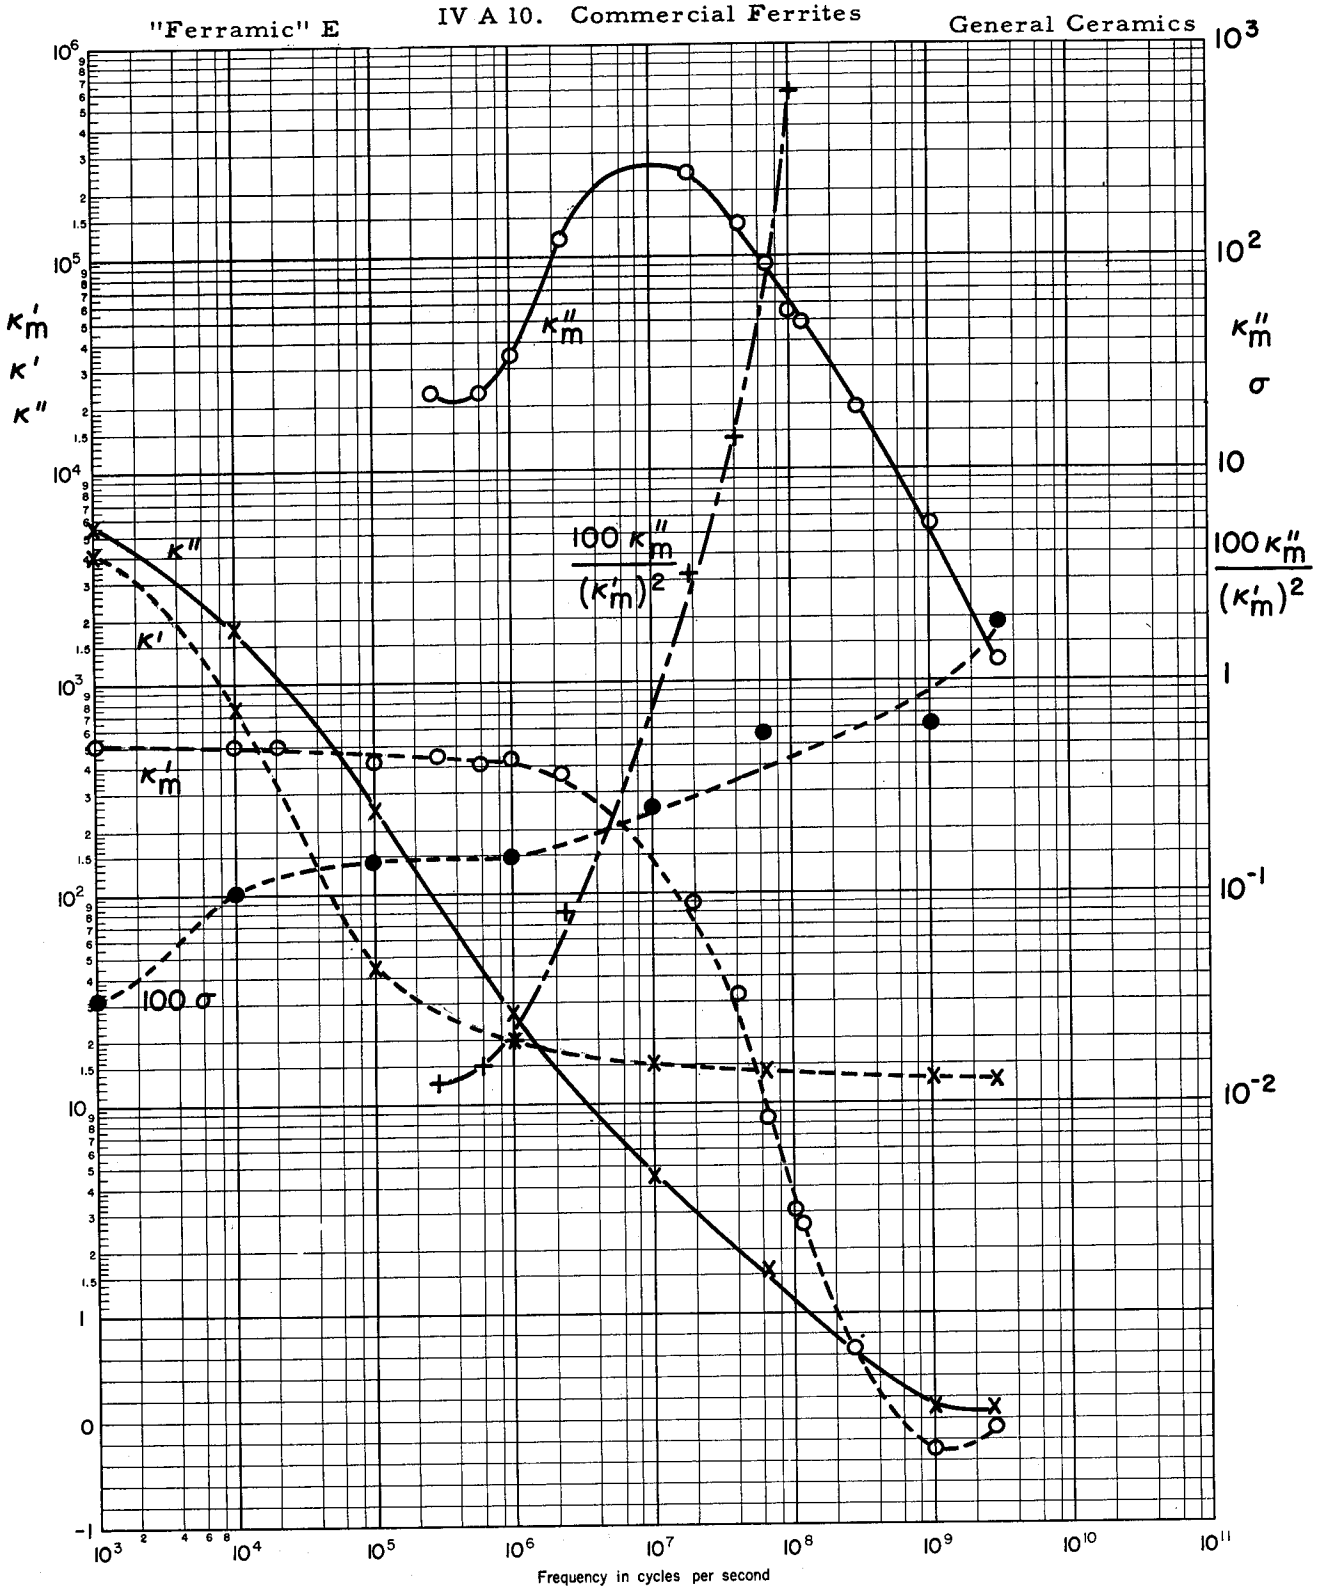


IV A 10. Commercial Ferrites

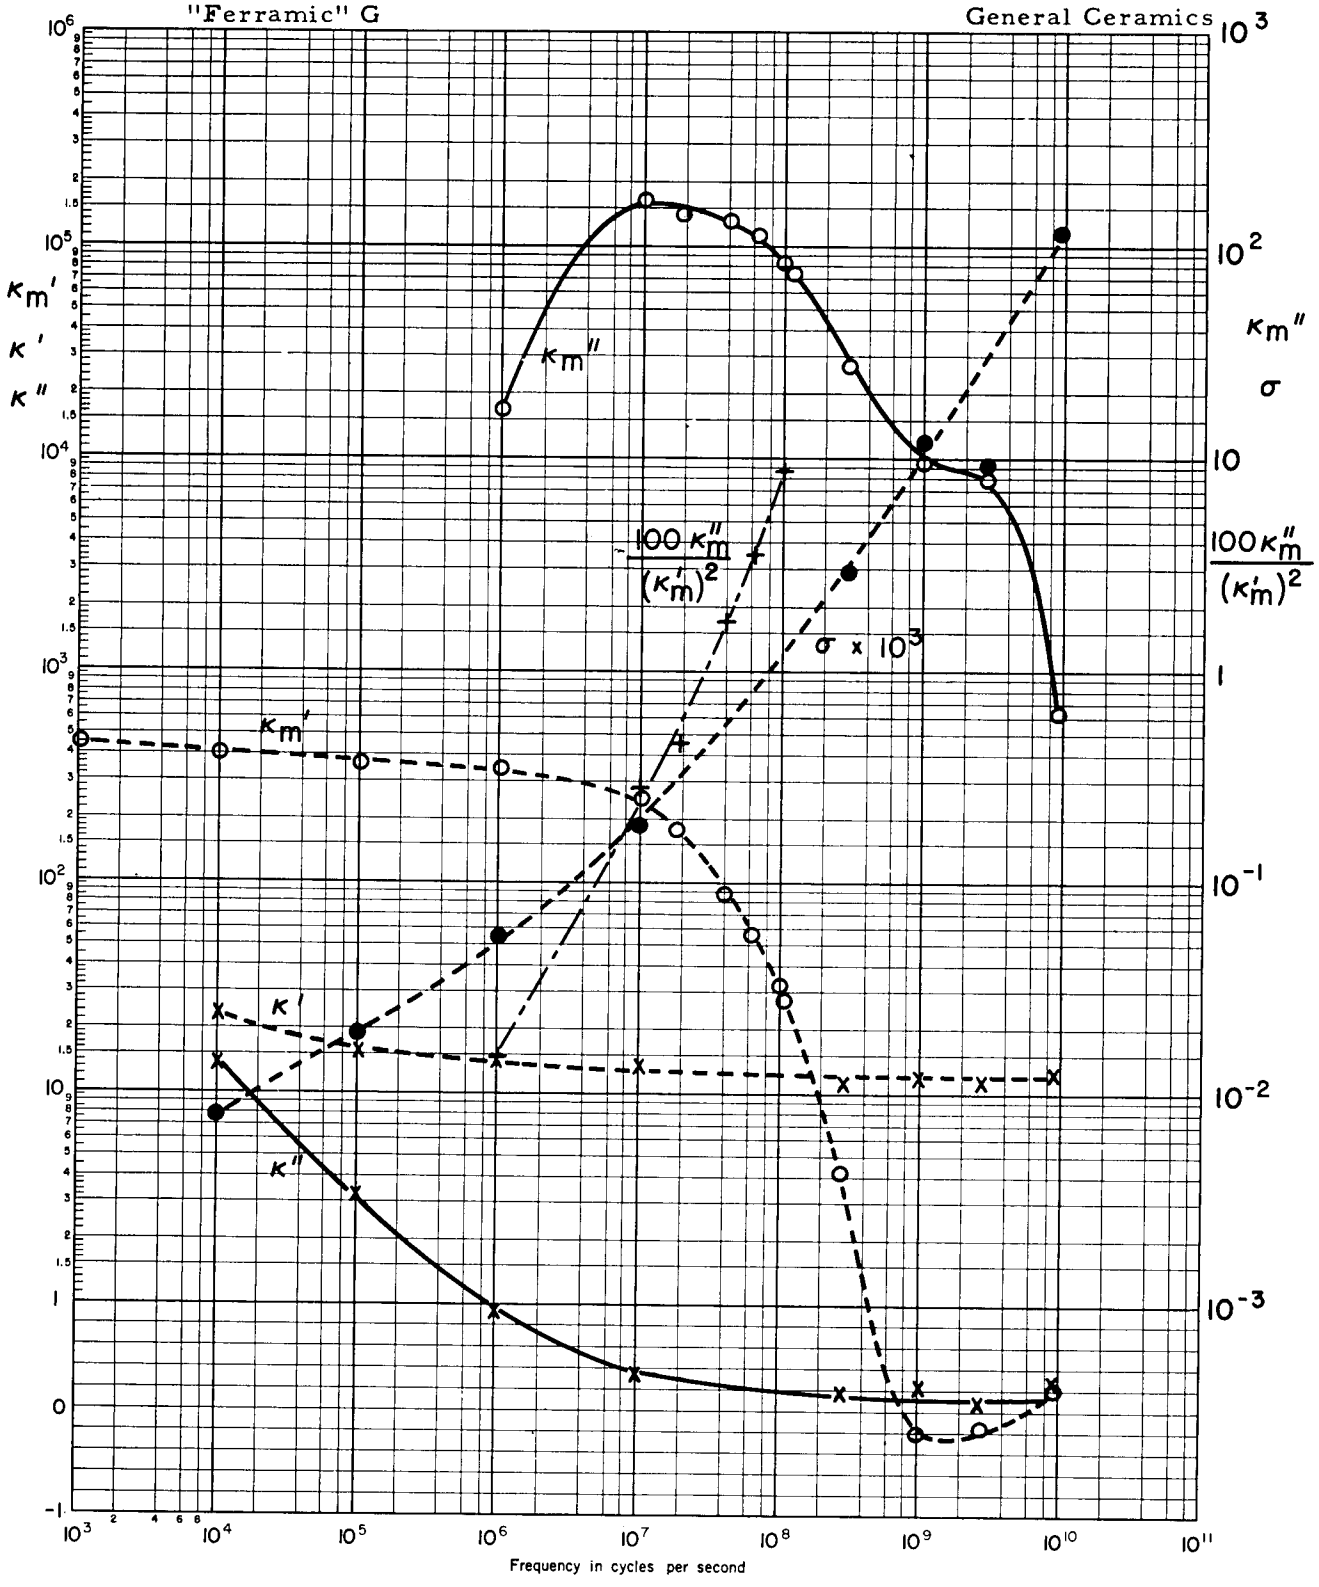


IV A 10. Commercial Ferrites

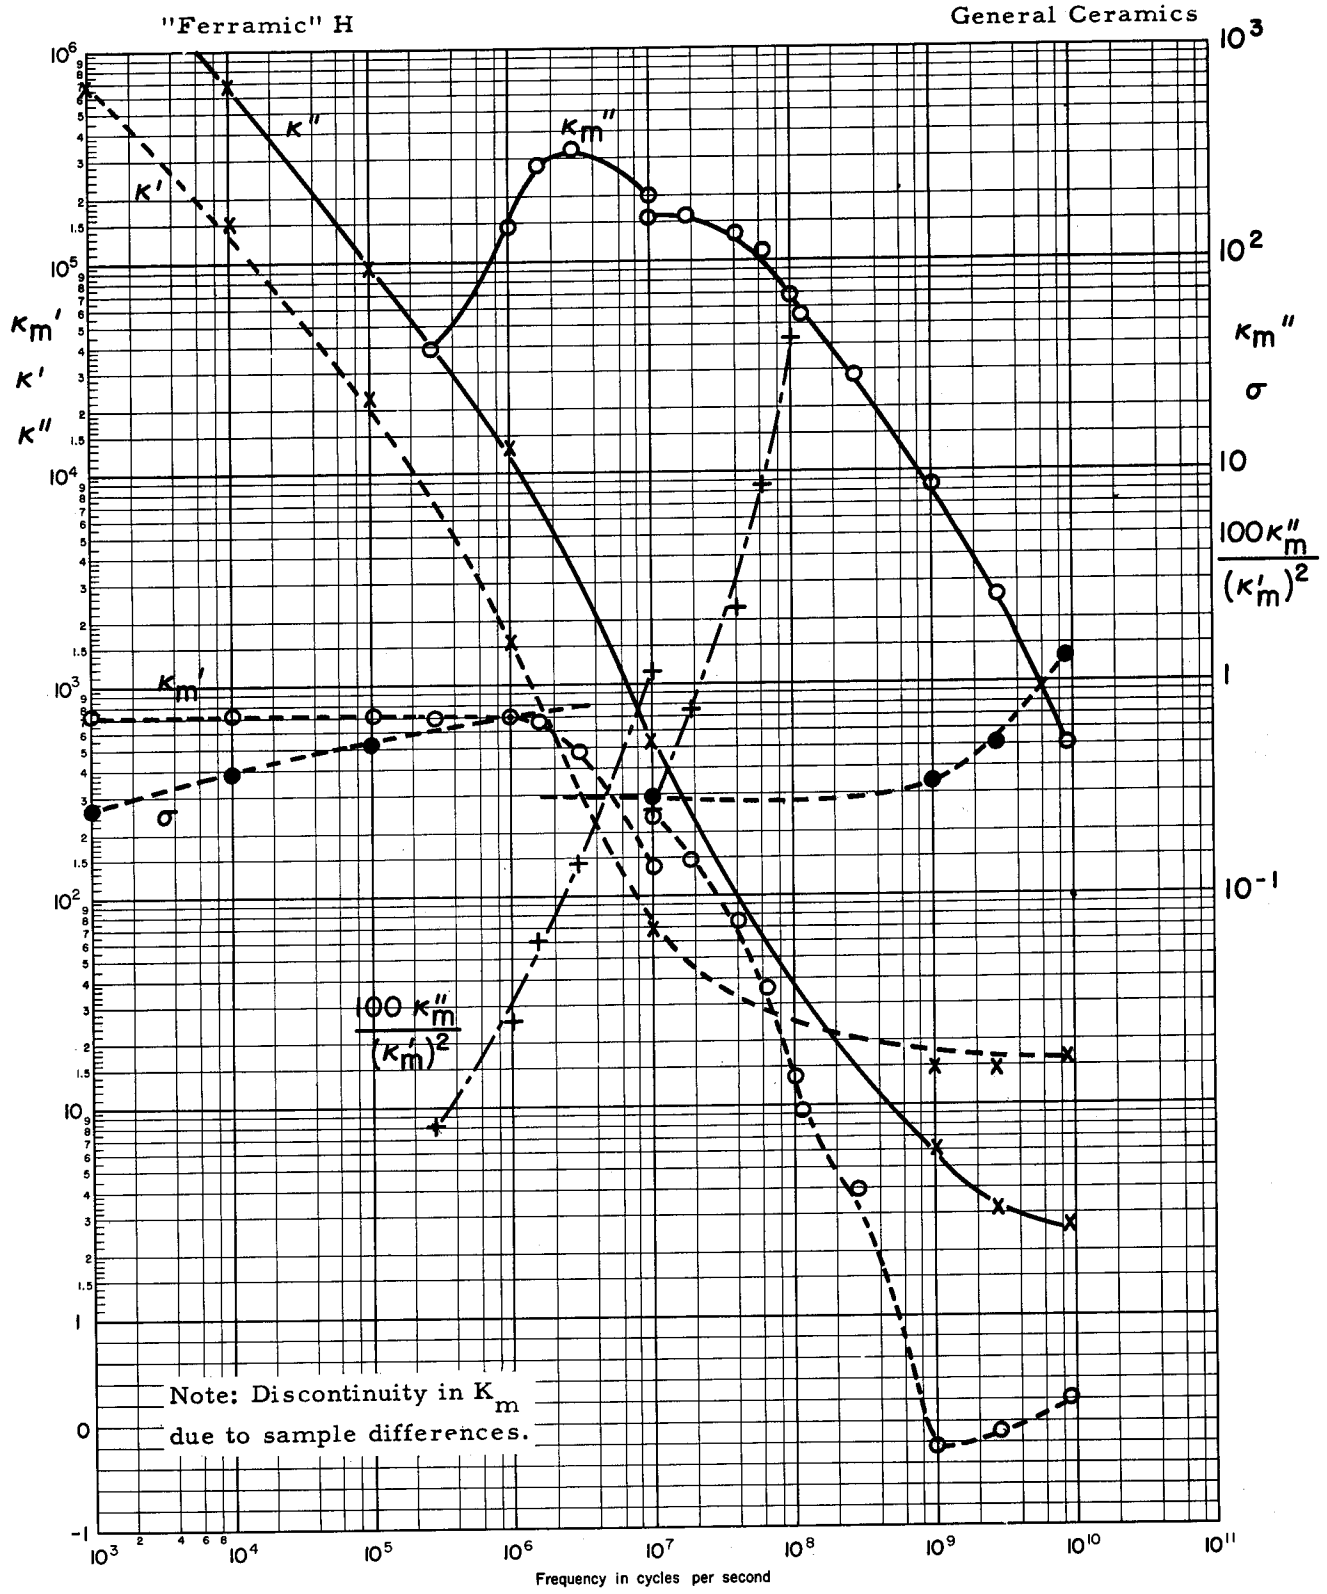


IV A 10. Commercial Ferrites

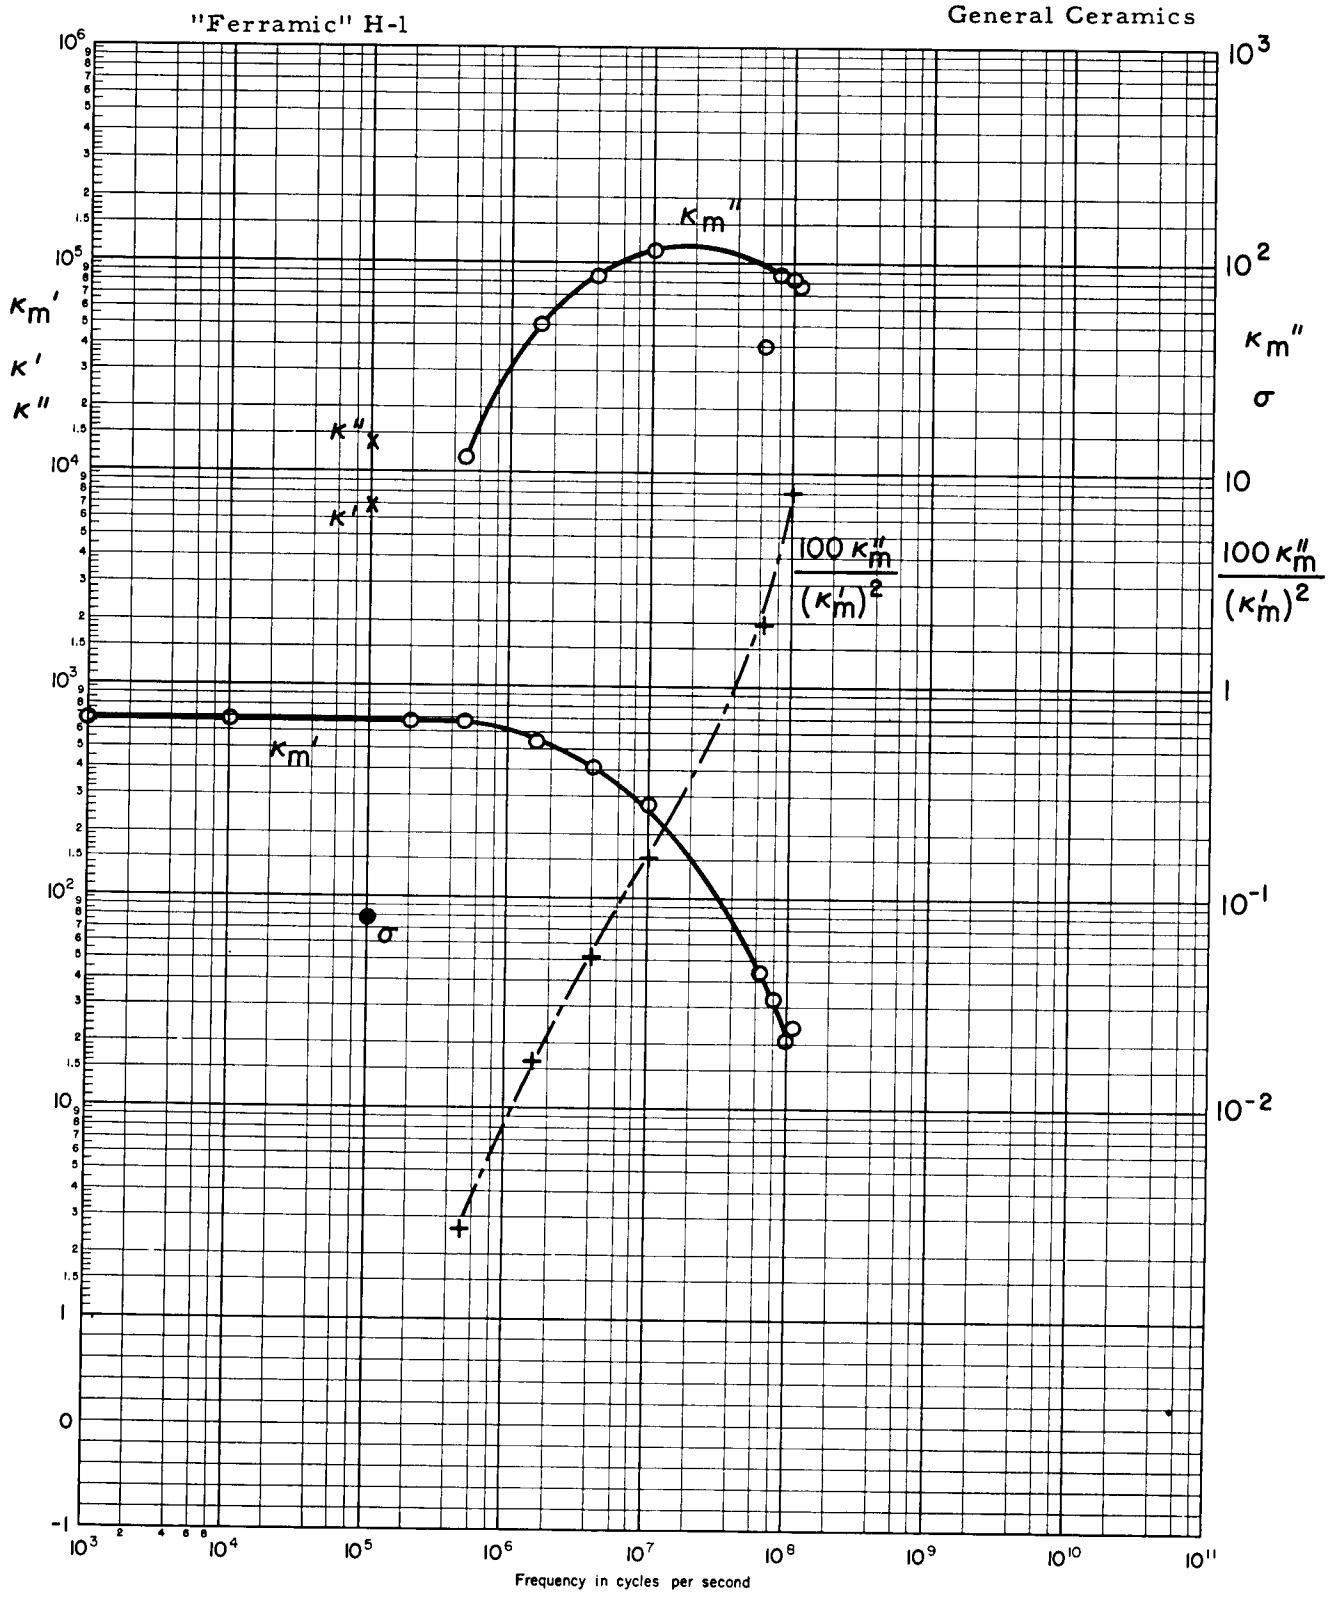


IV A 10. Commercial Ferrites

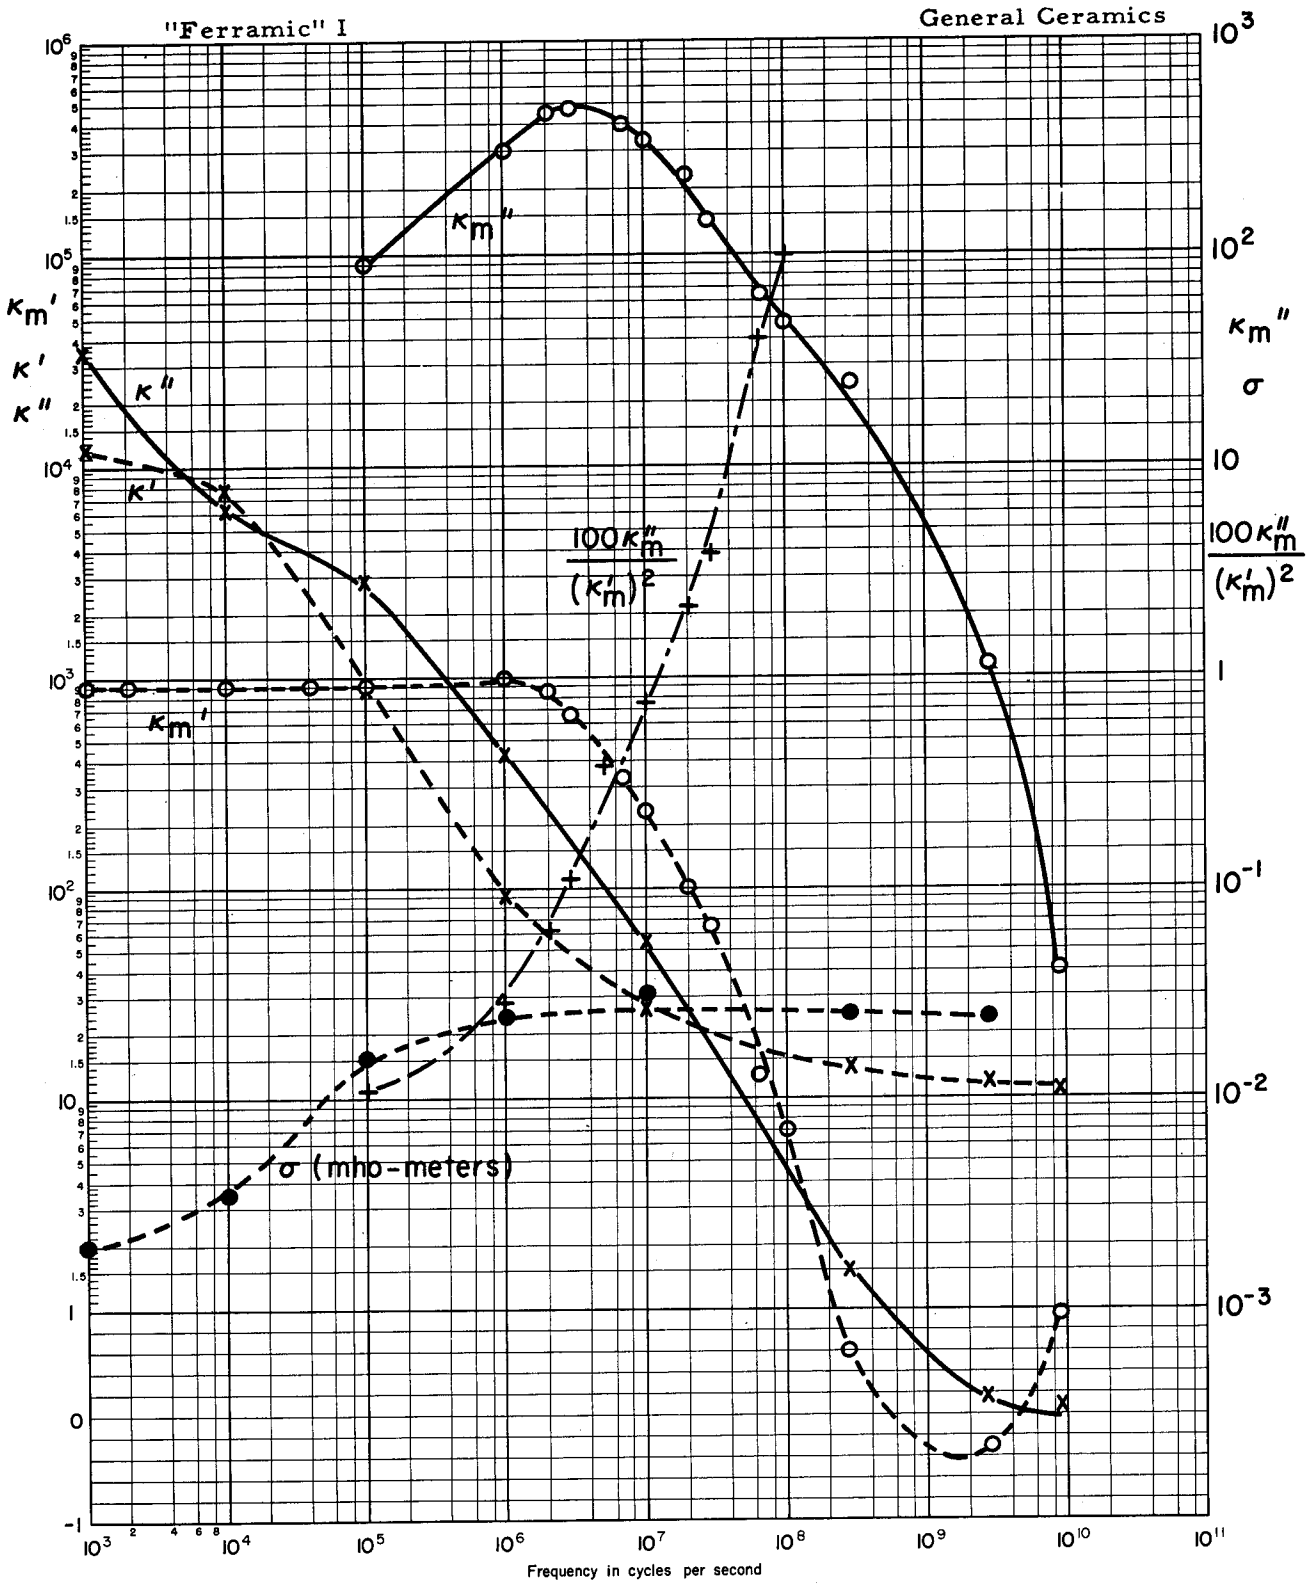


IV A 10. Commercial Ferrites

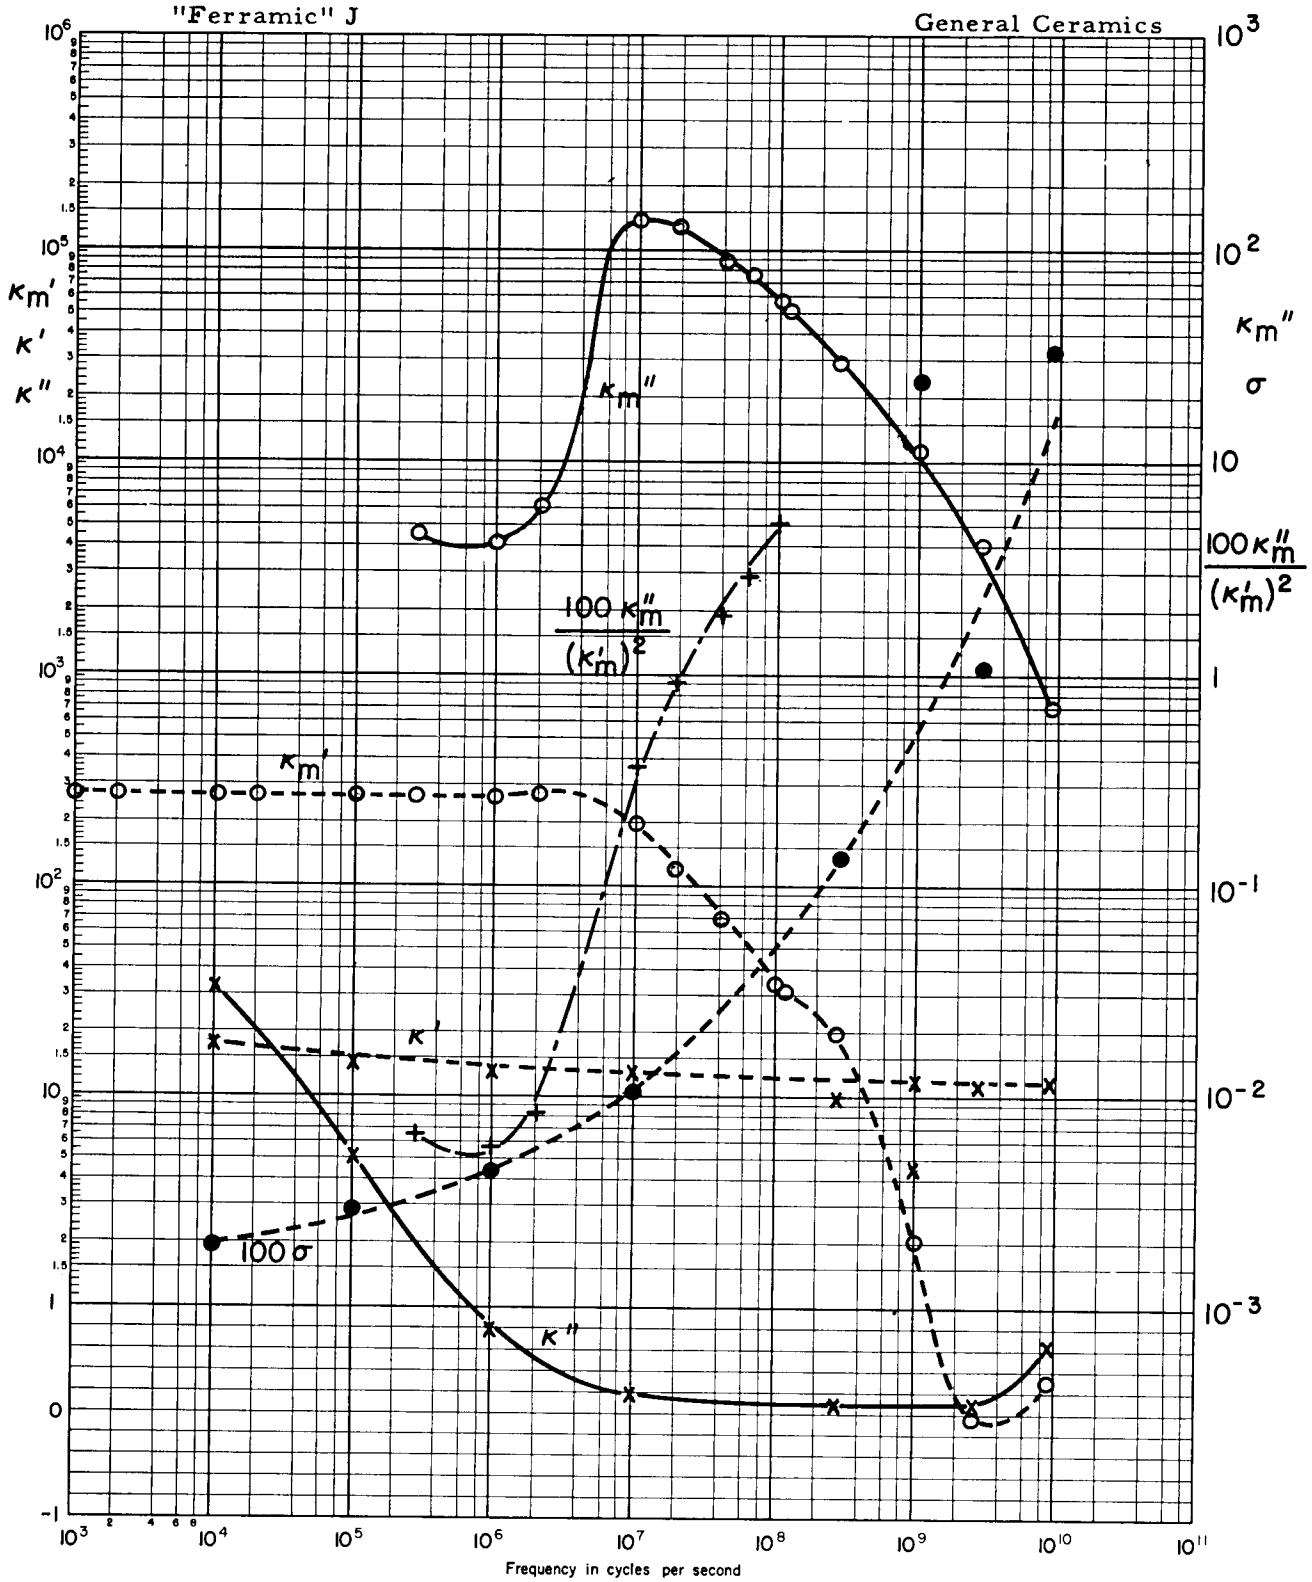

IV A 10. Commercial Ferrites

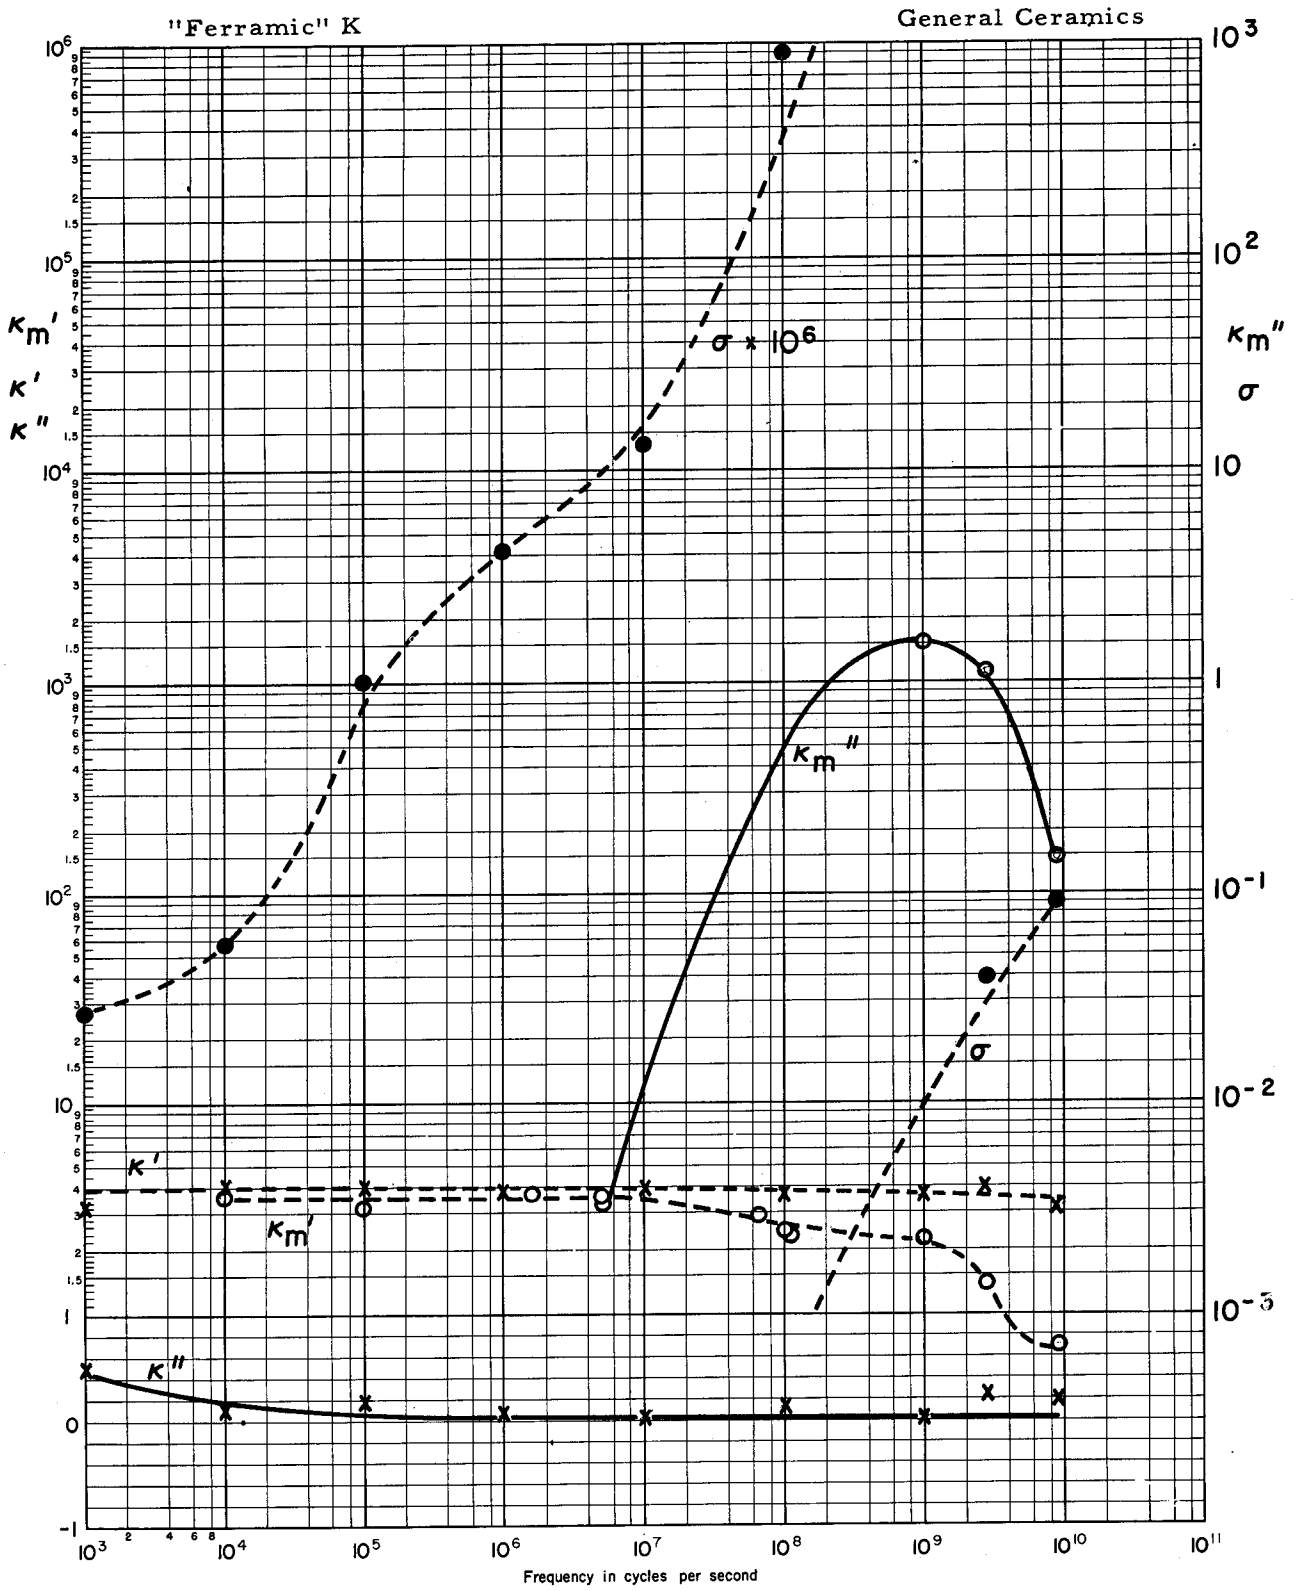


IV A 10. Commercial Ferrites

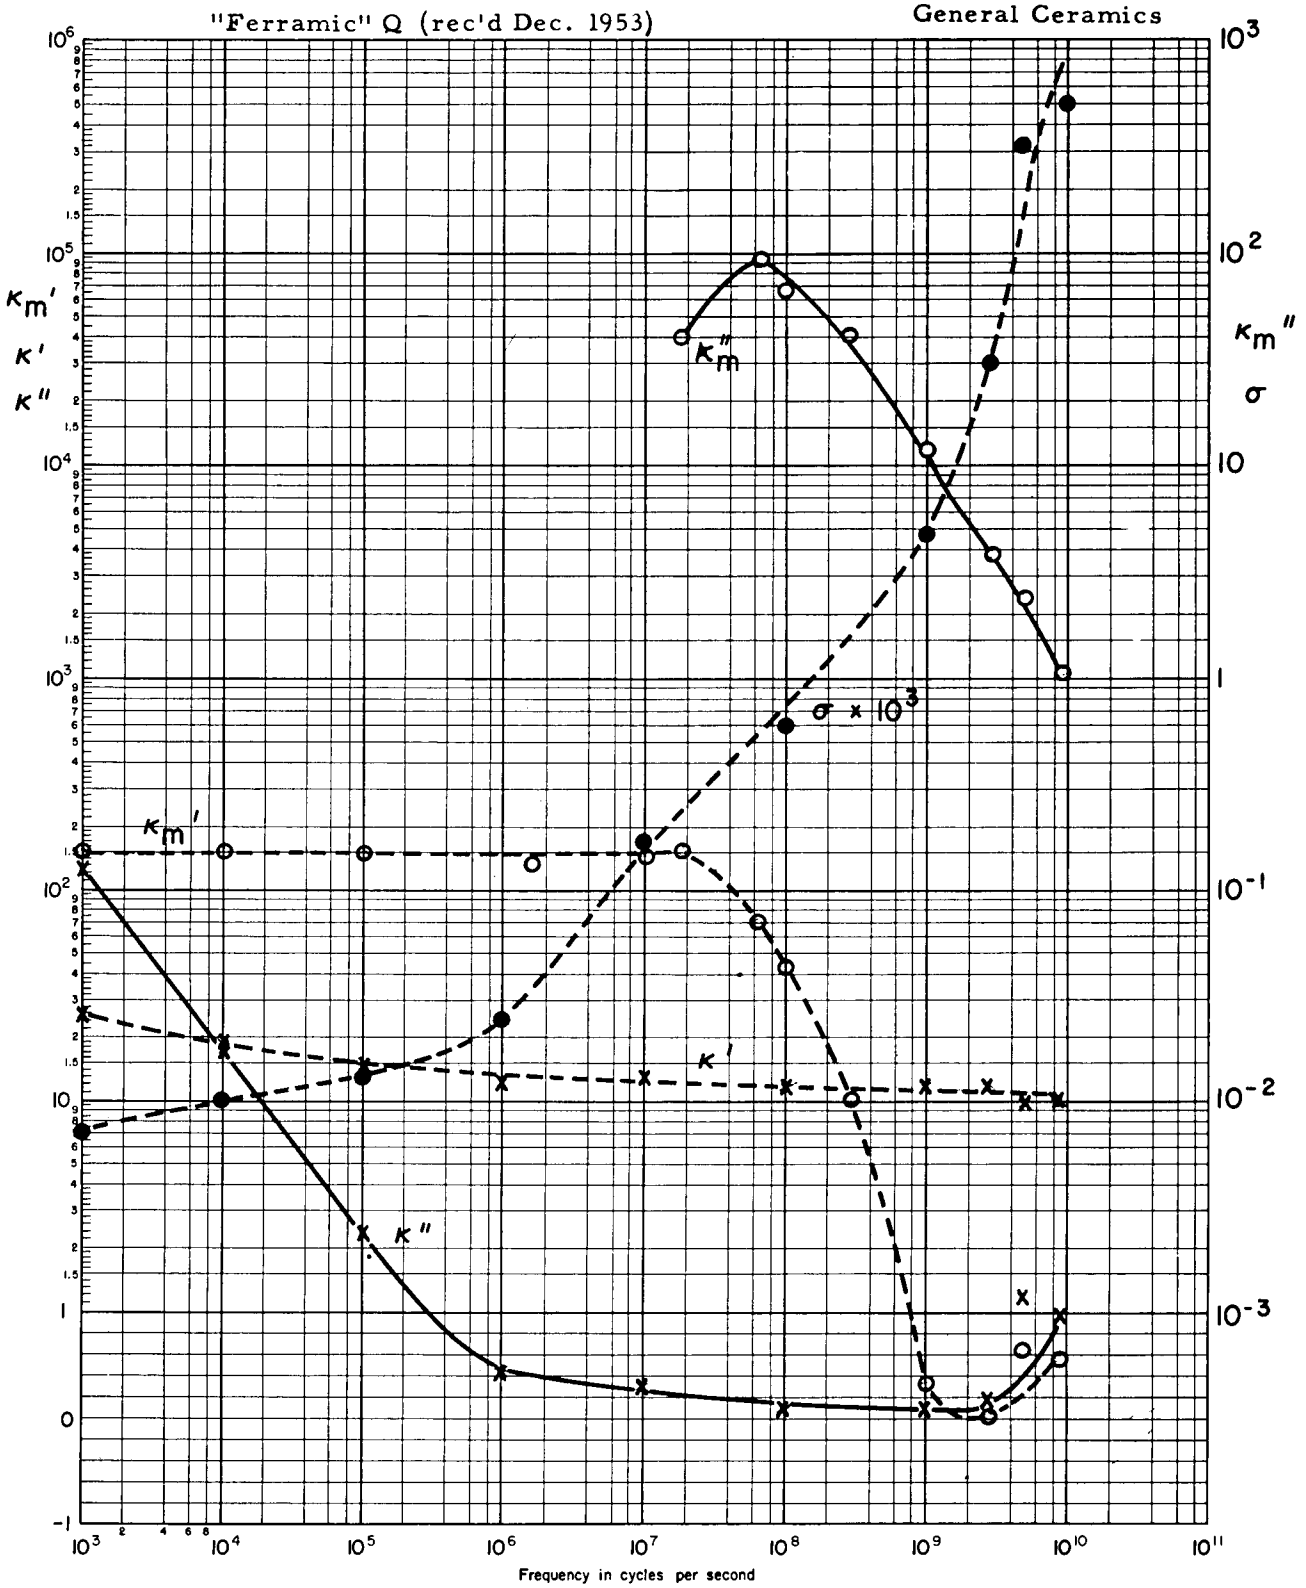


IV A 10. Commercial Ferrites


"Ferramic" Q (rec'd Aug. 1954) General Ceramics

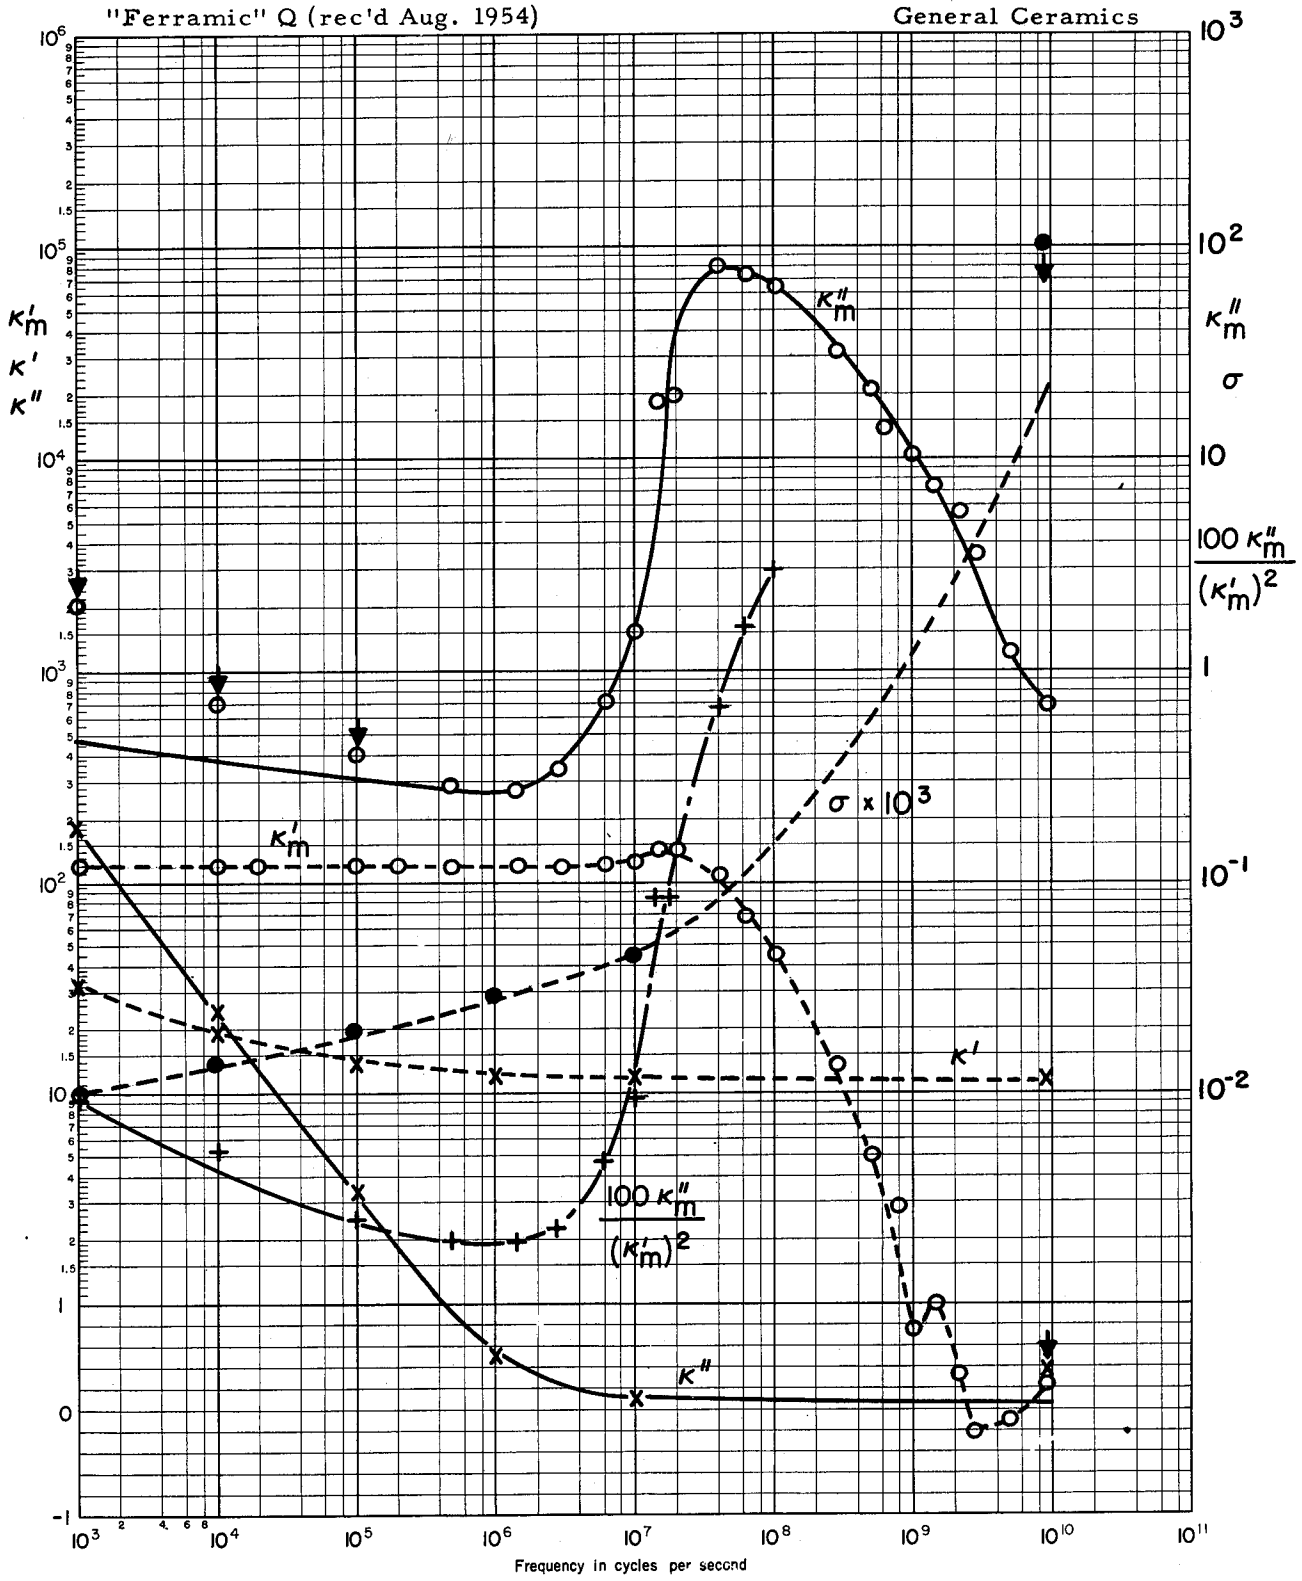


IV A 10. Commercial Ferrites

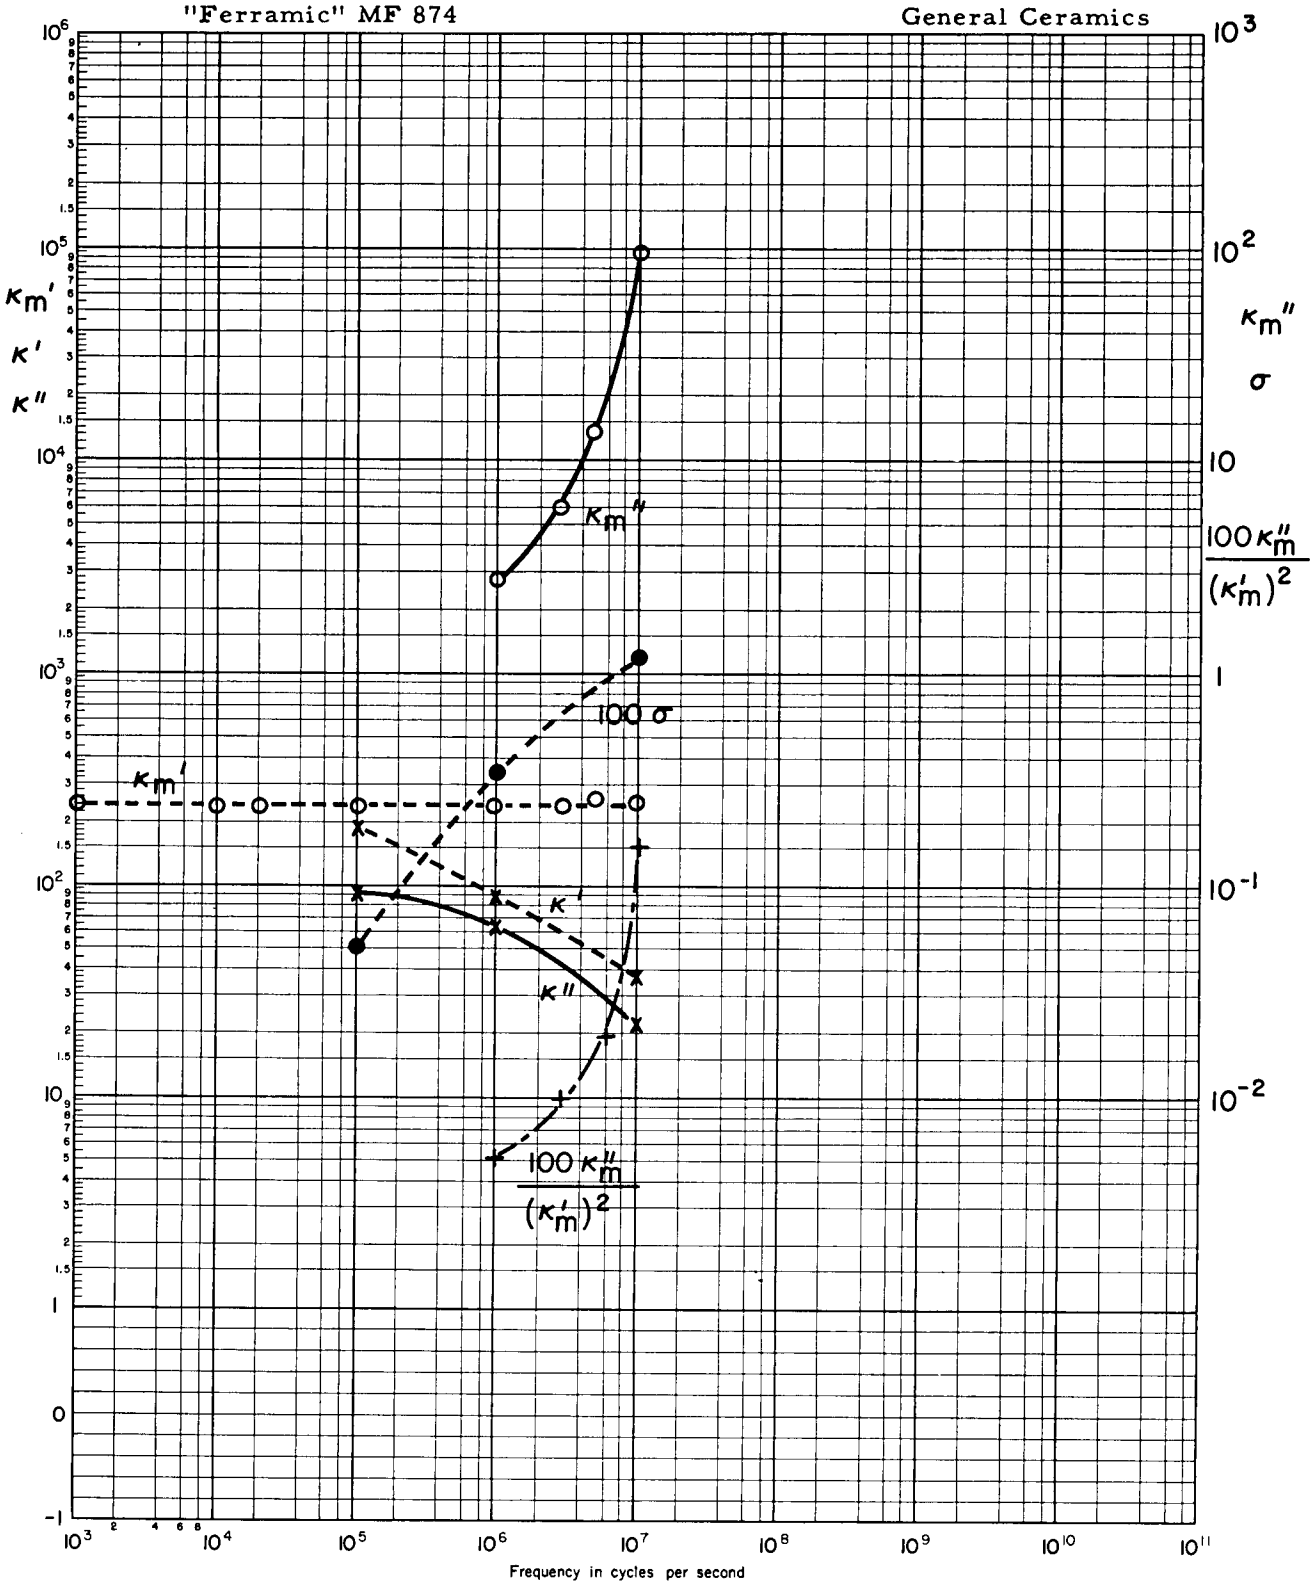


IV A 10. Commercial Ferrites

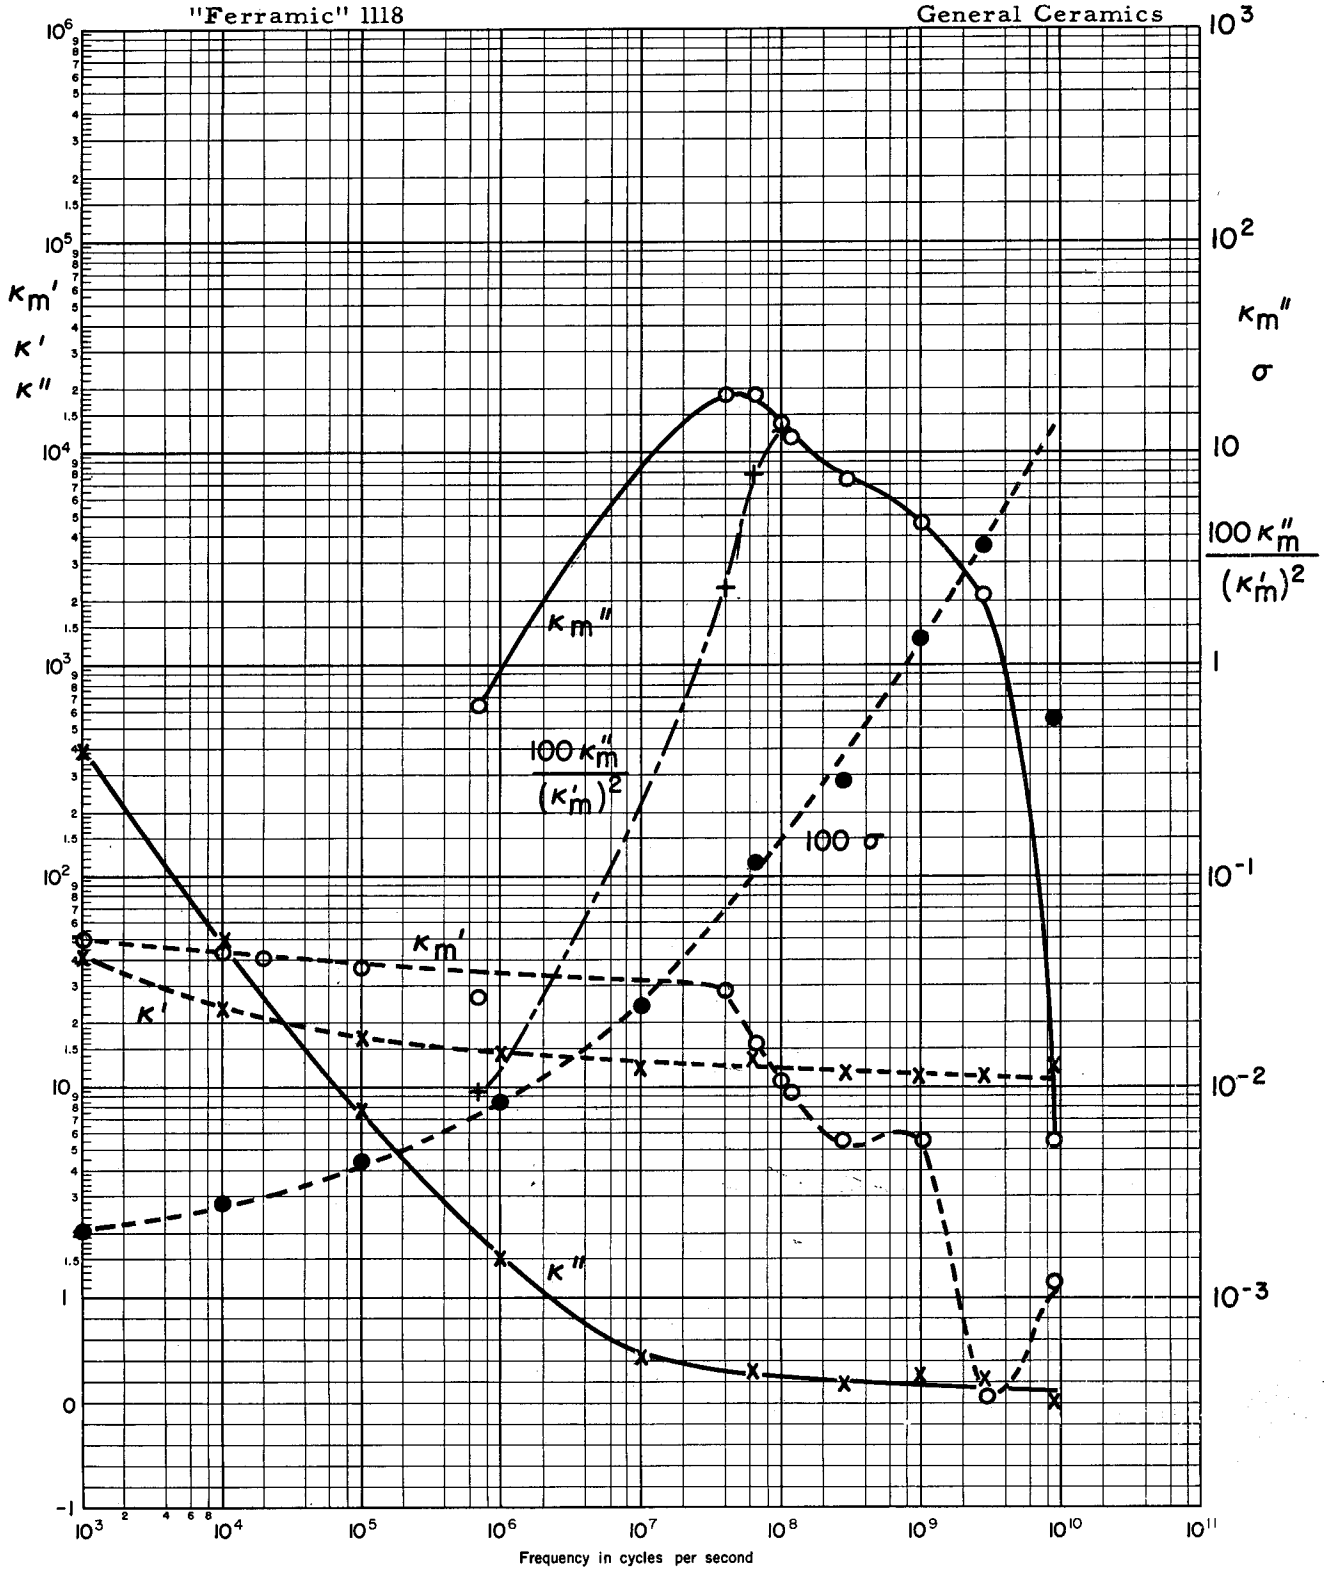

IV A 10. Commercial Ferrites

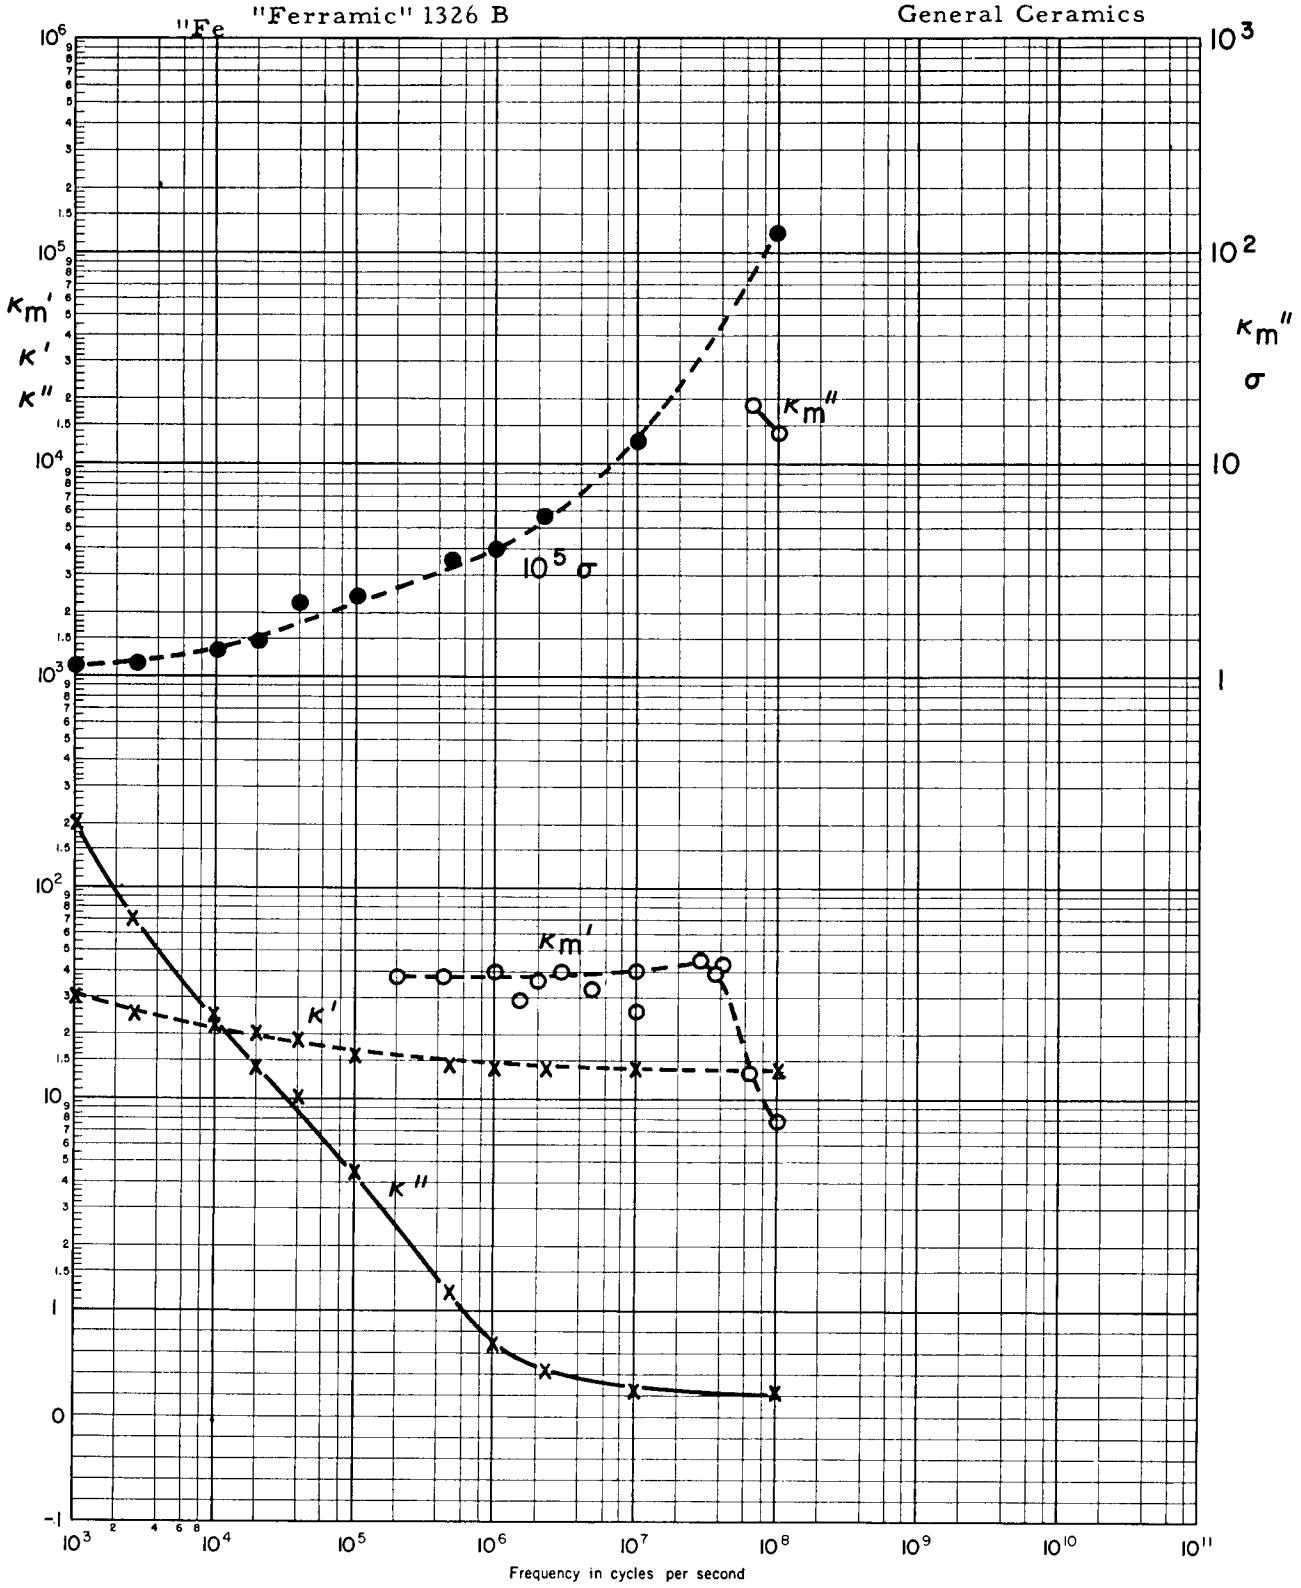


IV A 10. Commercial Ferrites

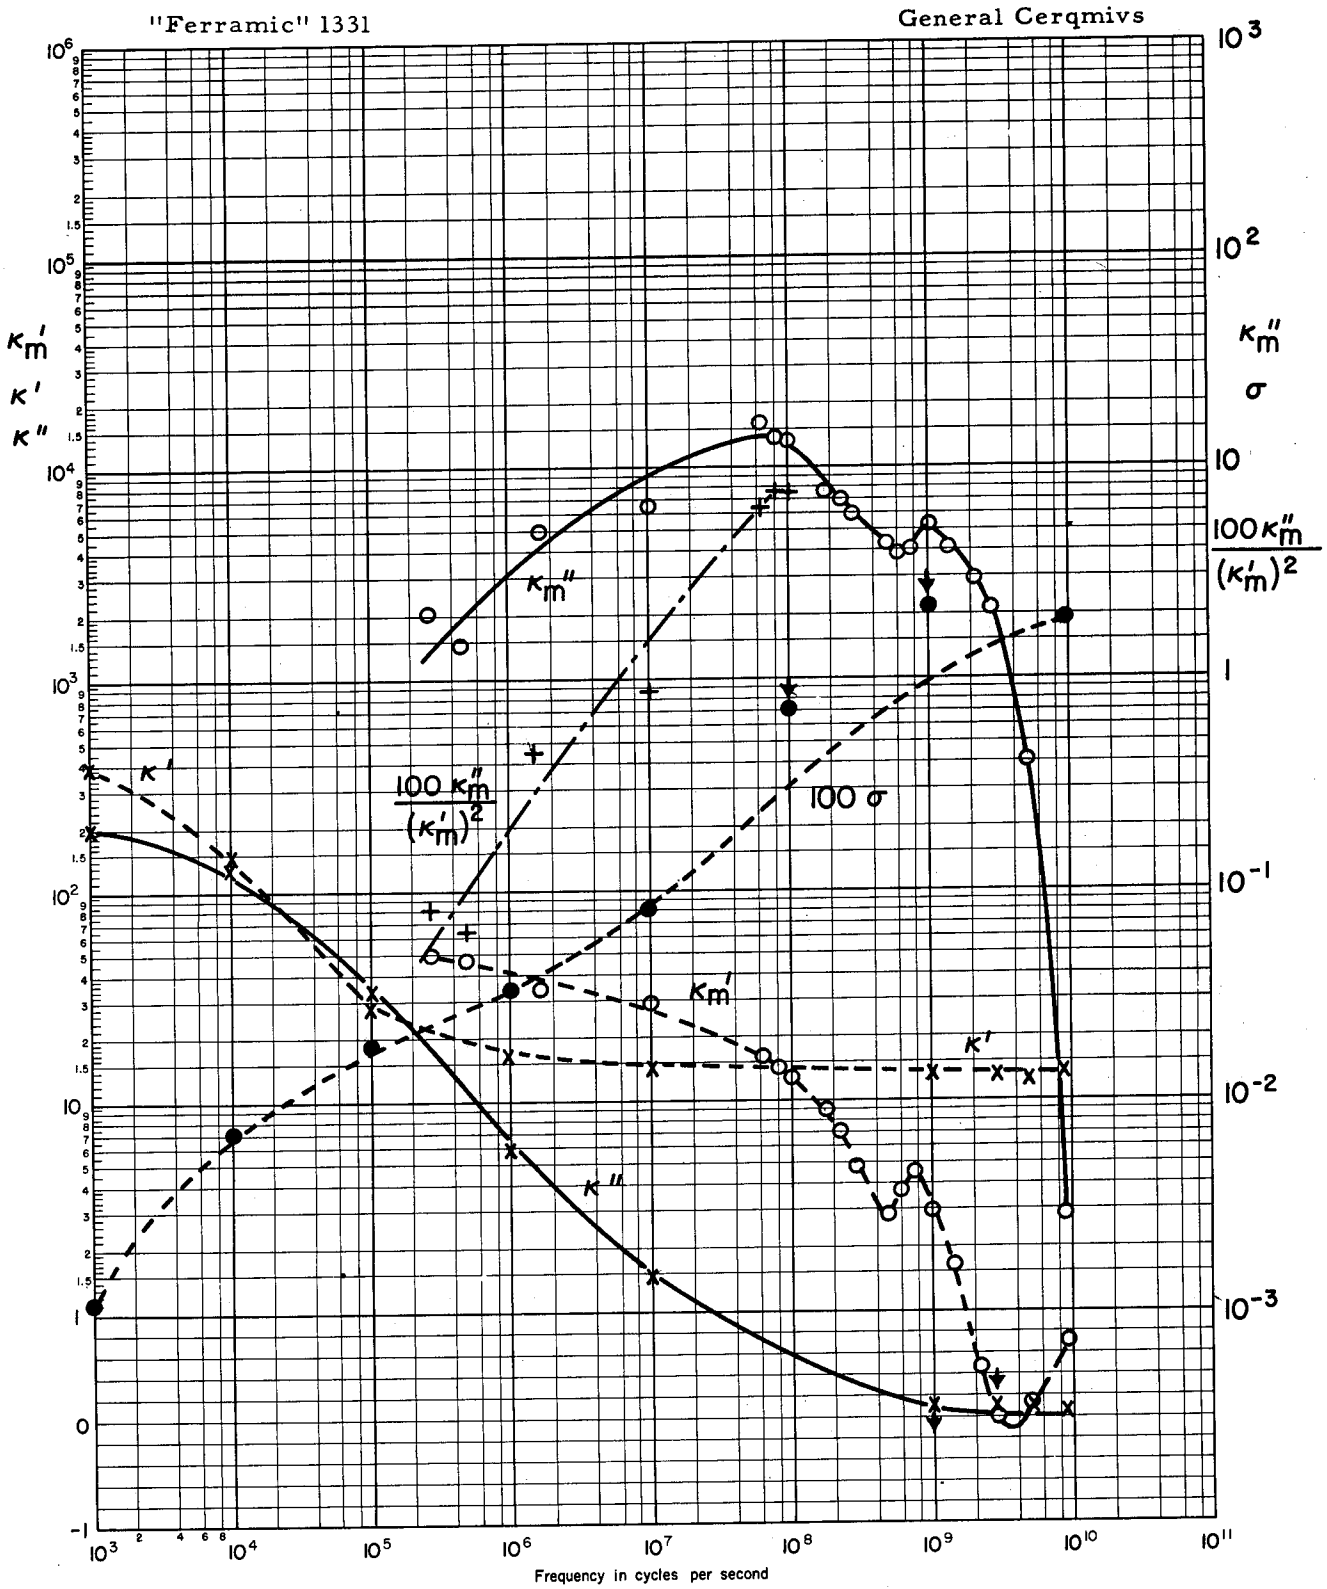

IV A 10. Commercial Ferrites

"Ferramic" 3310 (experimental)

General Ceramics

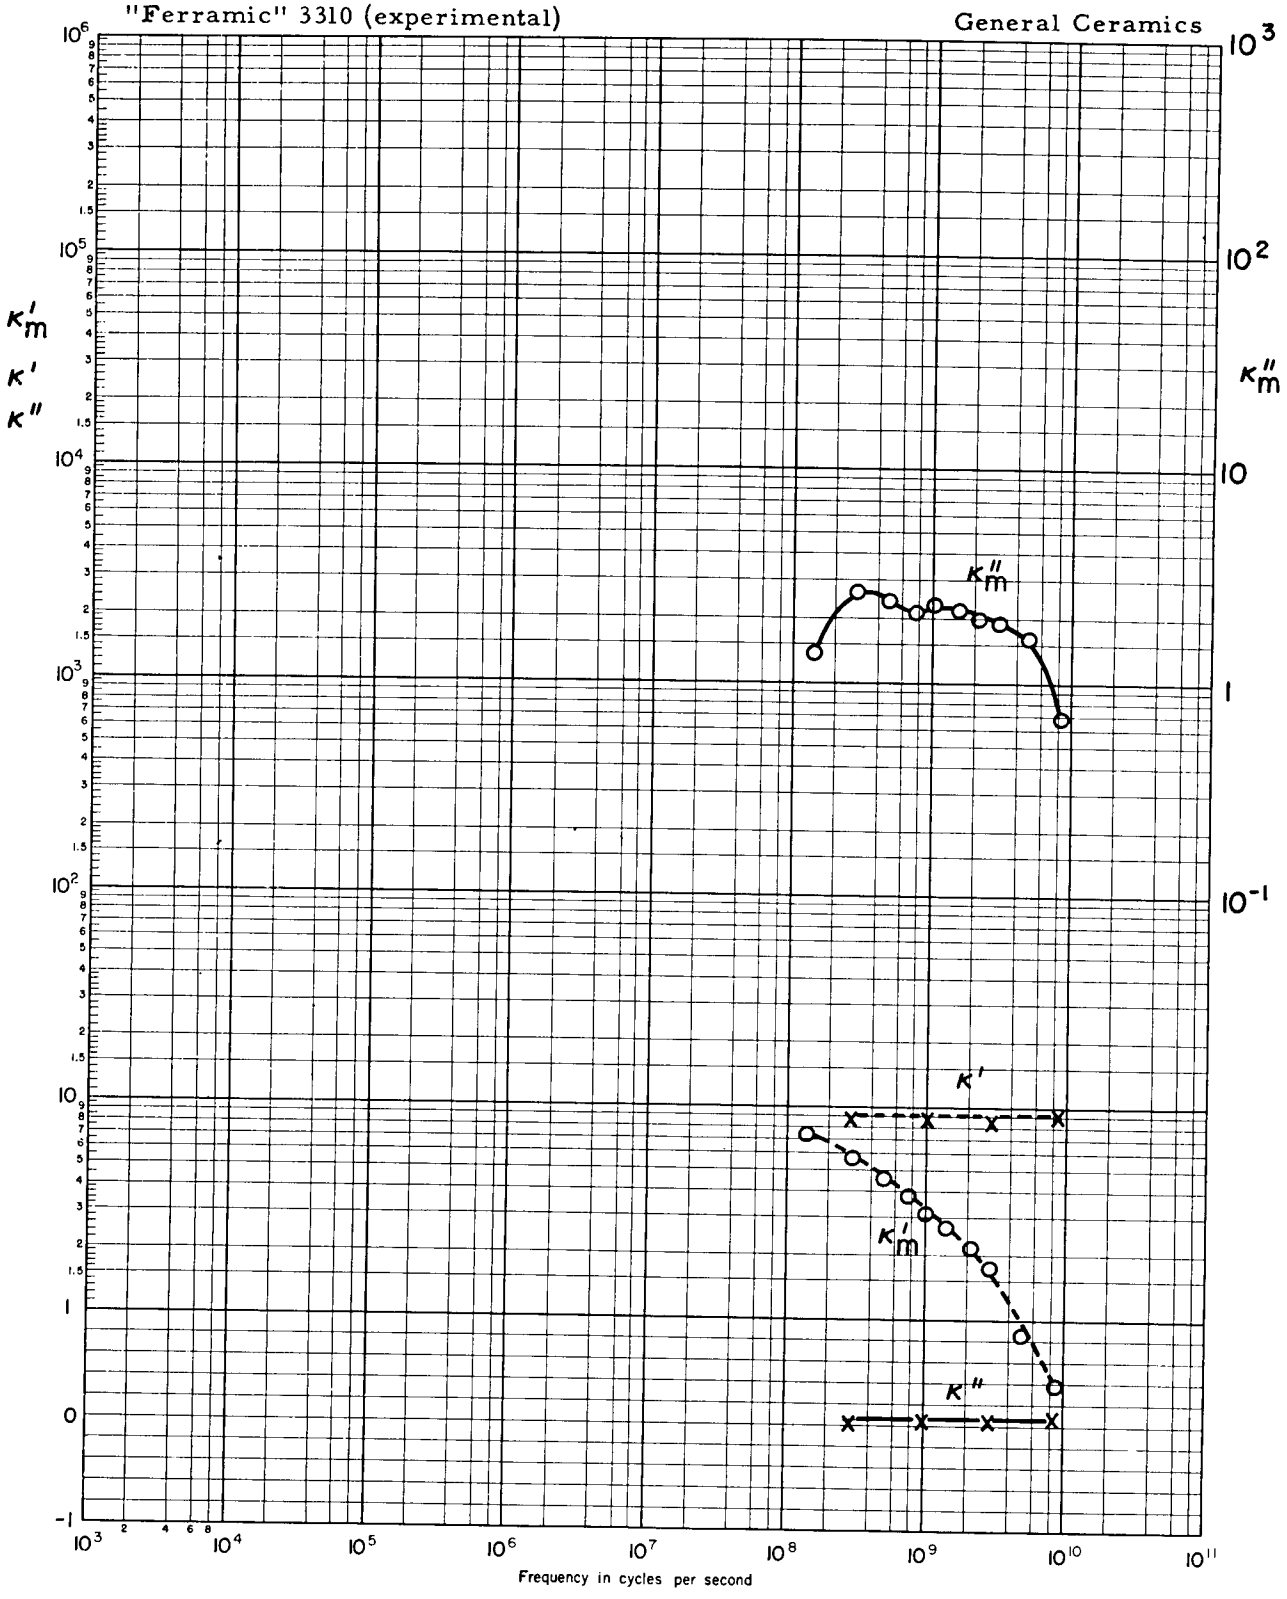


IV B. Hysteresis Loops and Saturation Magnetization

1. Cobalt Ferrite, High Density Ceramic

$CoFe_2O_4$ (T = 33°C)


Lab. Ins. Res.

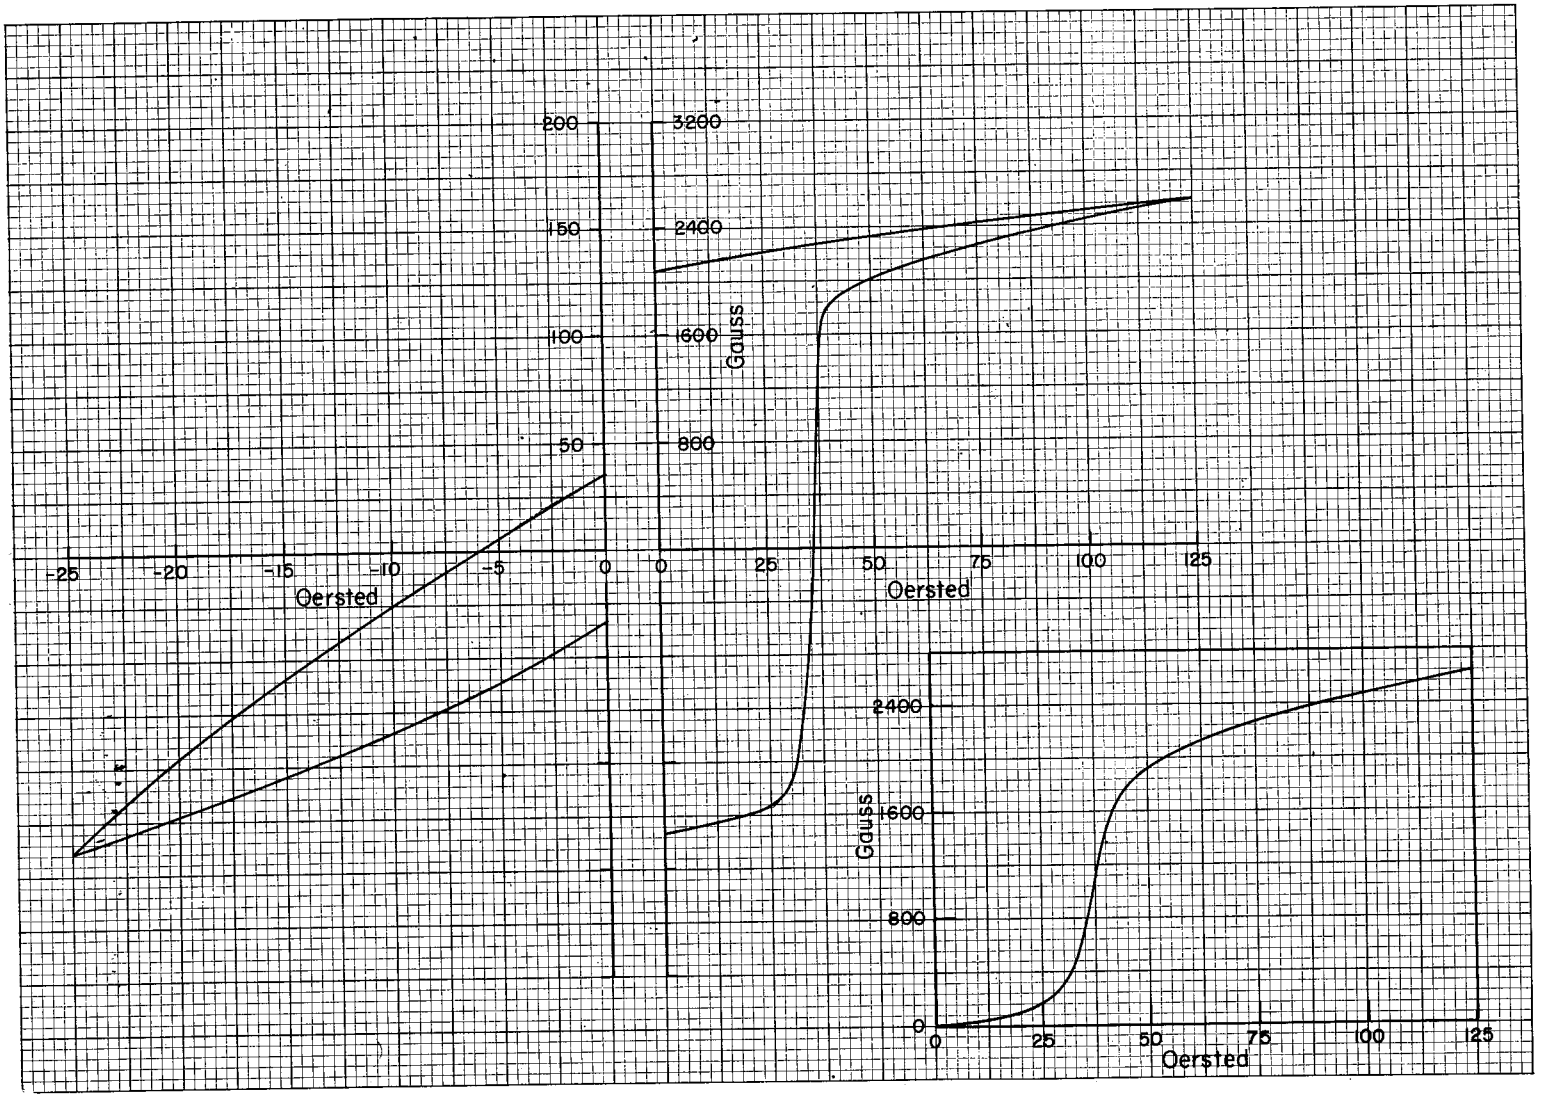

IV B 2. Lithium-Nickel Ferrite Ceramic

$(LiO)_{0.1517}(NiO)_{0.045}(Fe_2O_3)_{0.8035}$ ($T = 28^{\circ}C$)


M.I.T. Lincoln Lab.

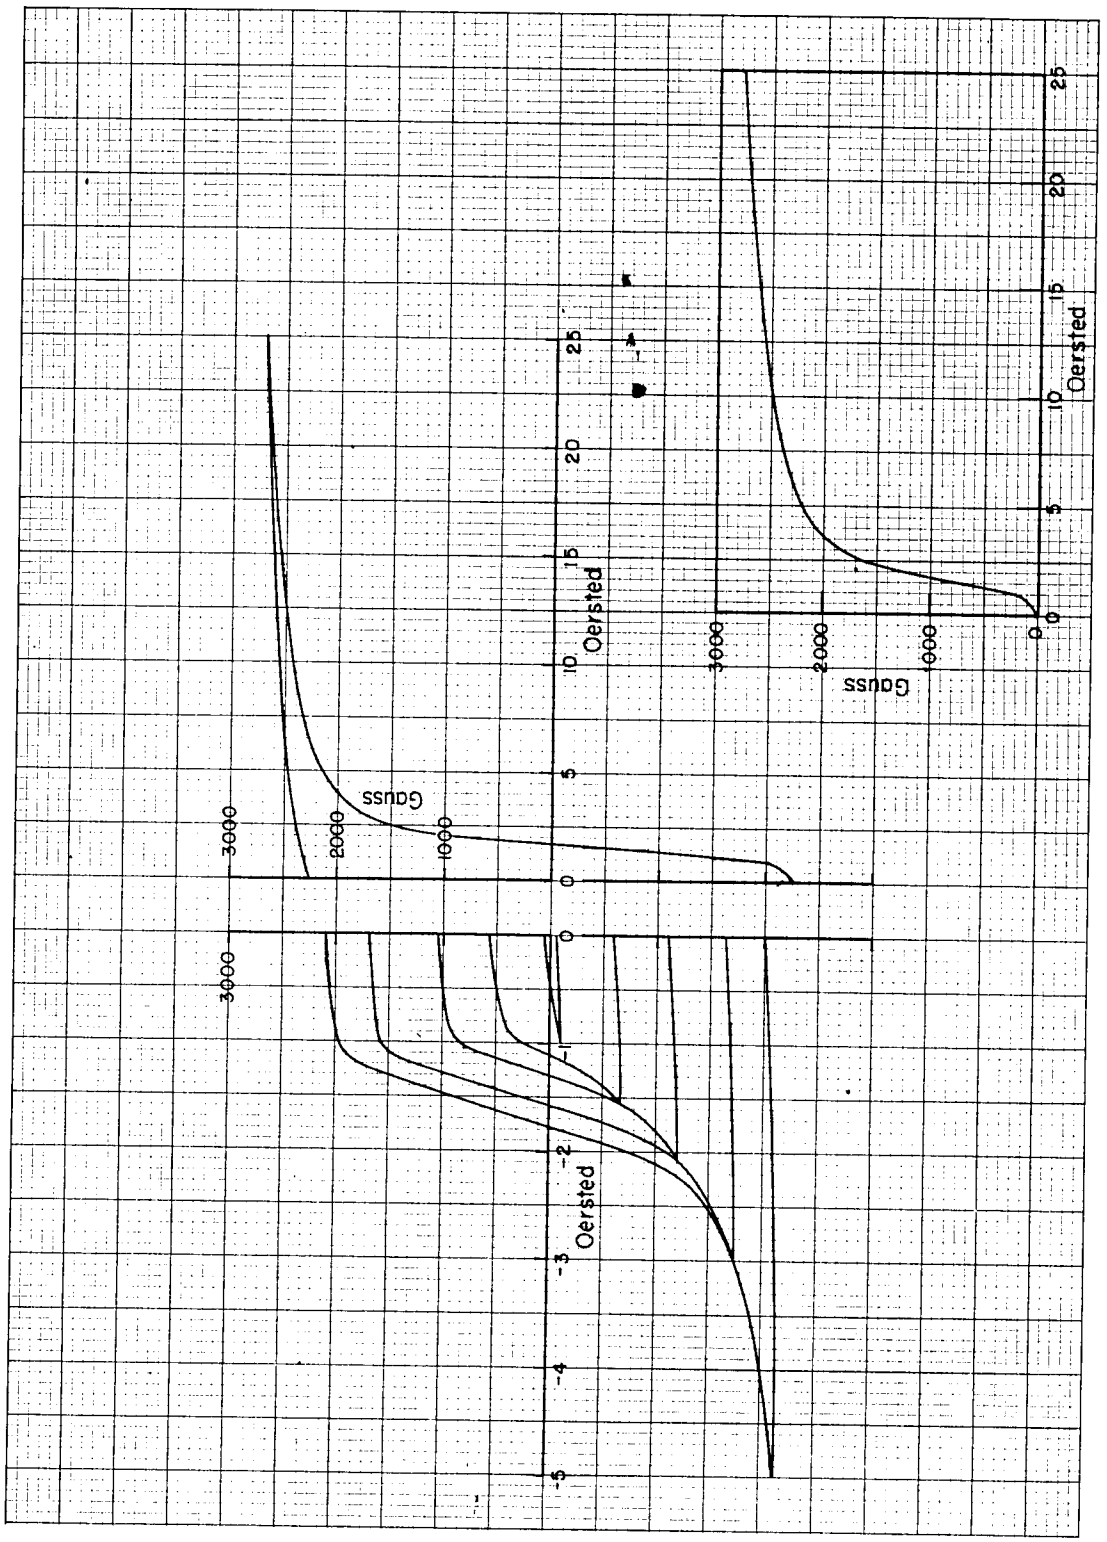

IV B 3. Magnesium Ferrite, High Density Ceramic

$MgFe_2O_4$ (T = 29°C)


Lab. Ins. Res.

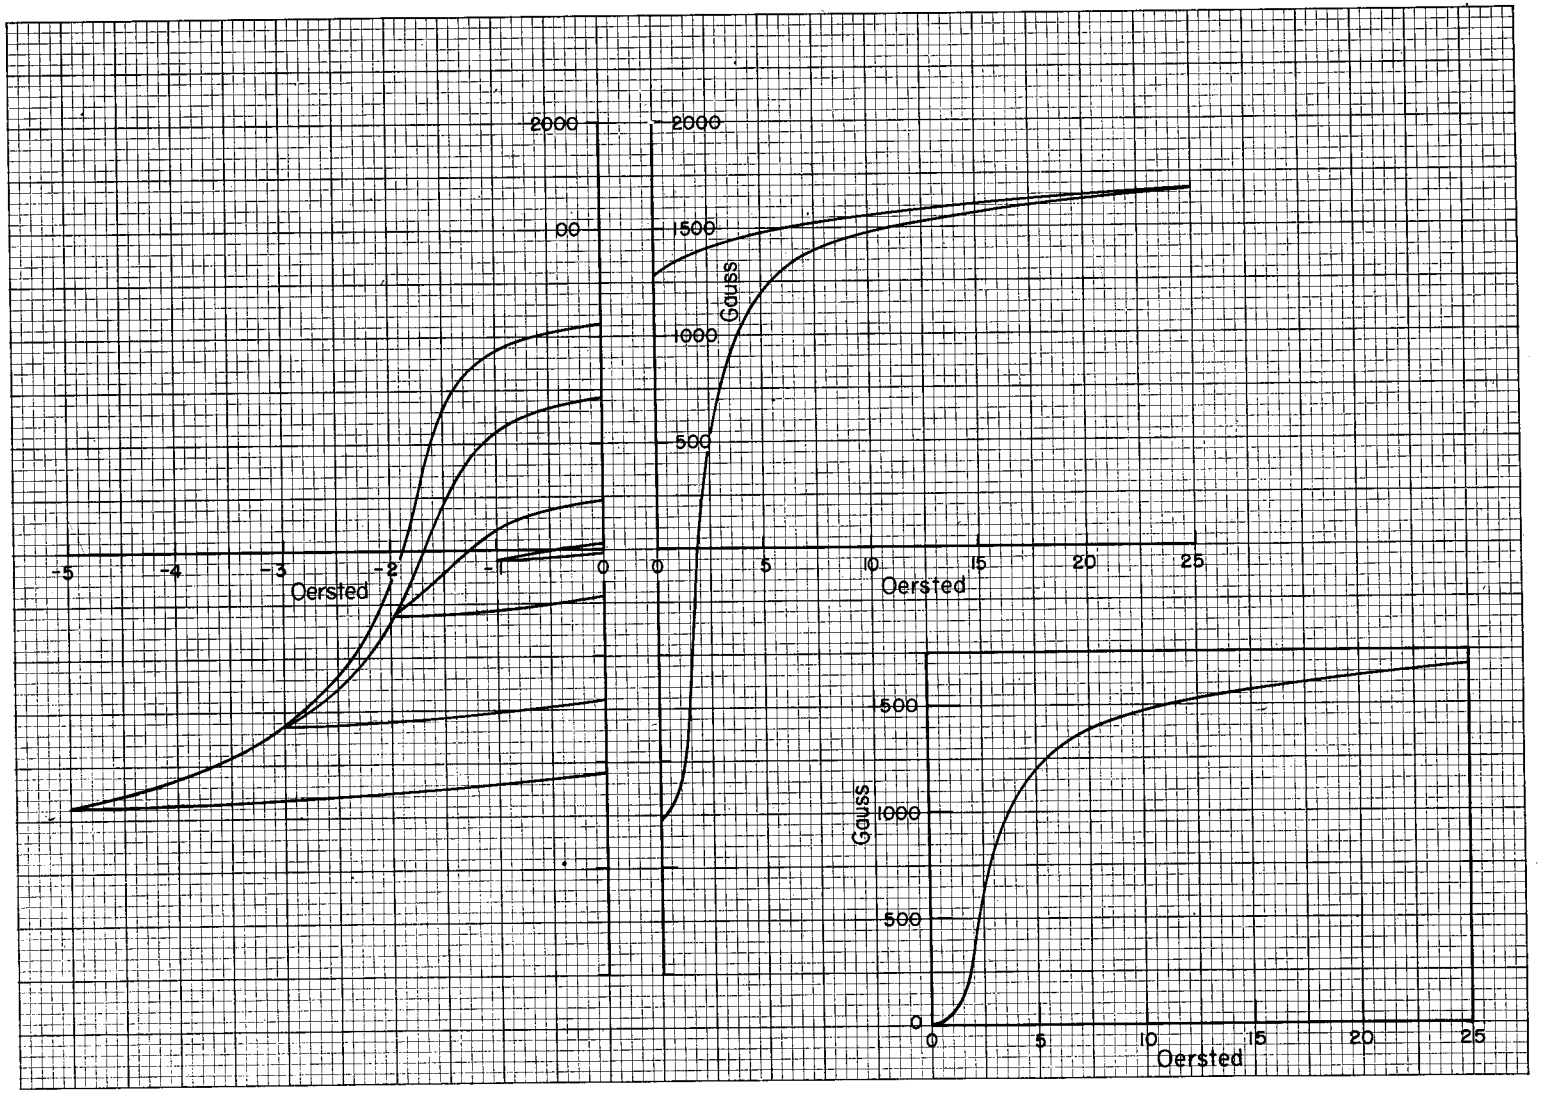

IV B 4. Magnesium-Manganese Ferrite Ceramics


$(MgO)_{0.58}(MnO)_{0.06}(Fe_2O_3)_{0.36}$ (T = 26°C)

Lab. Ins. Res.

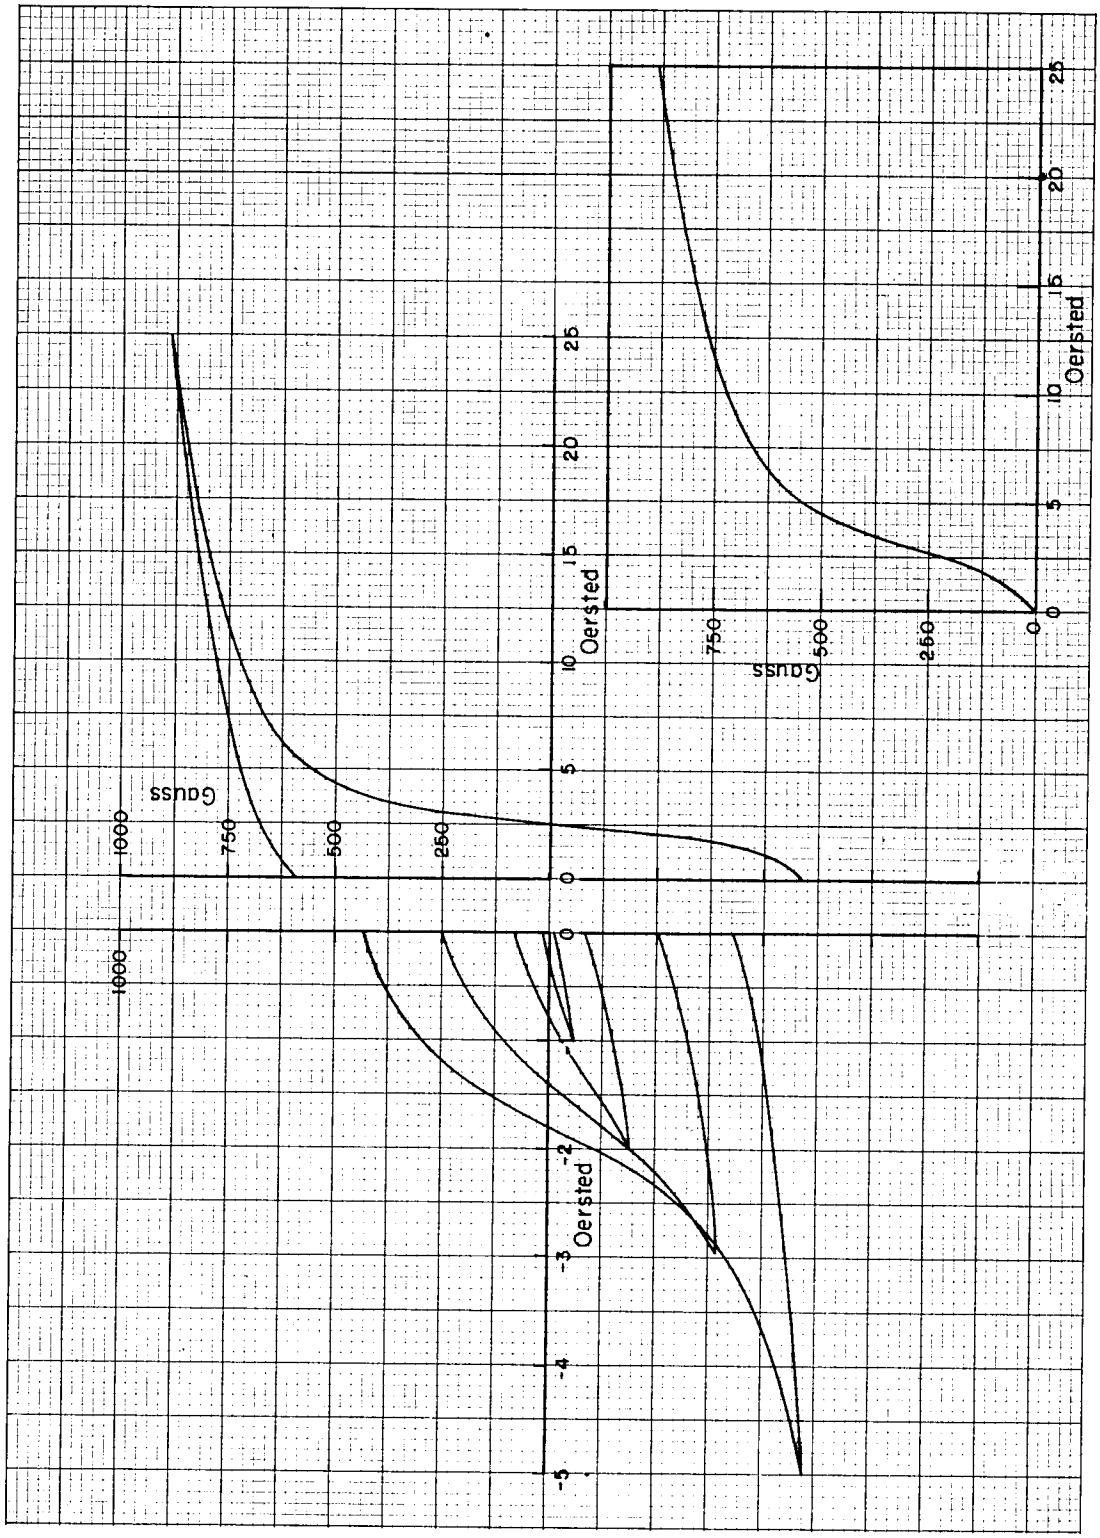

IV B 4. Magnesium-Manganese Ferrite Ceramics


$(MgO)_{0.38}(MnO)_{0.22}(Fe_2O_3)_{0.40}$ (T = 28°C) M.I.T. Lincoln Lab.

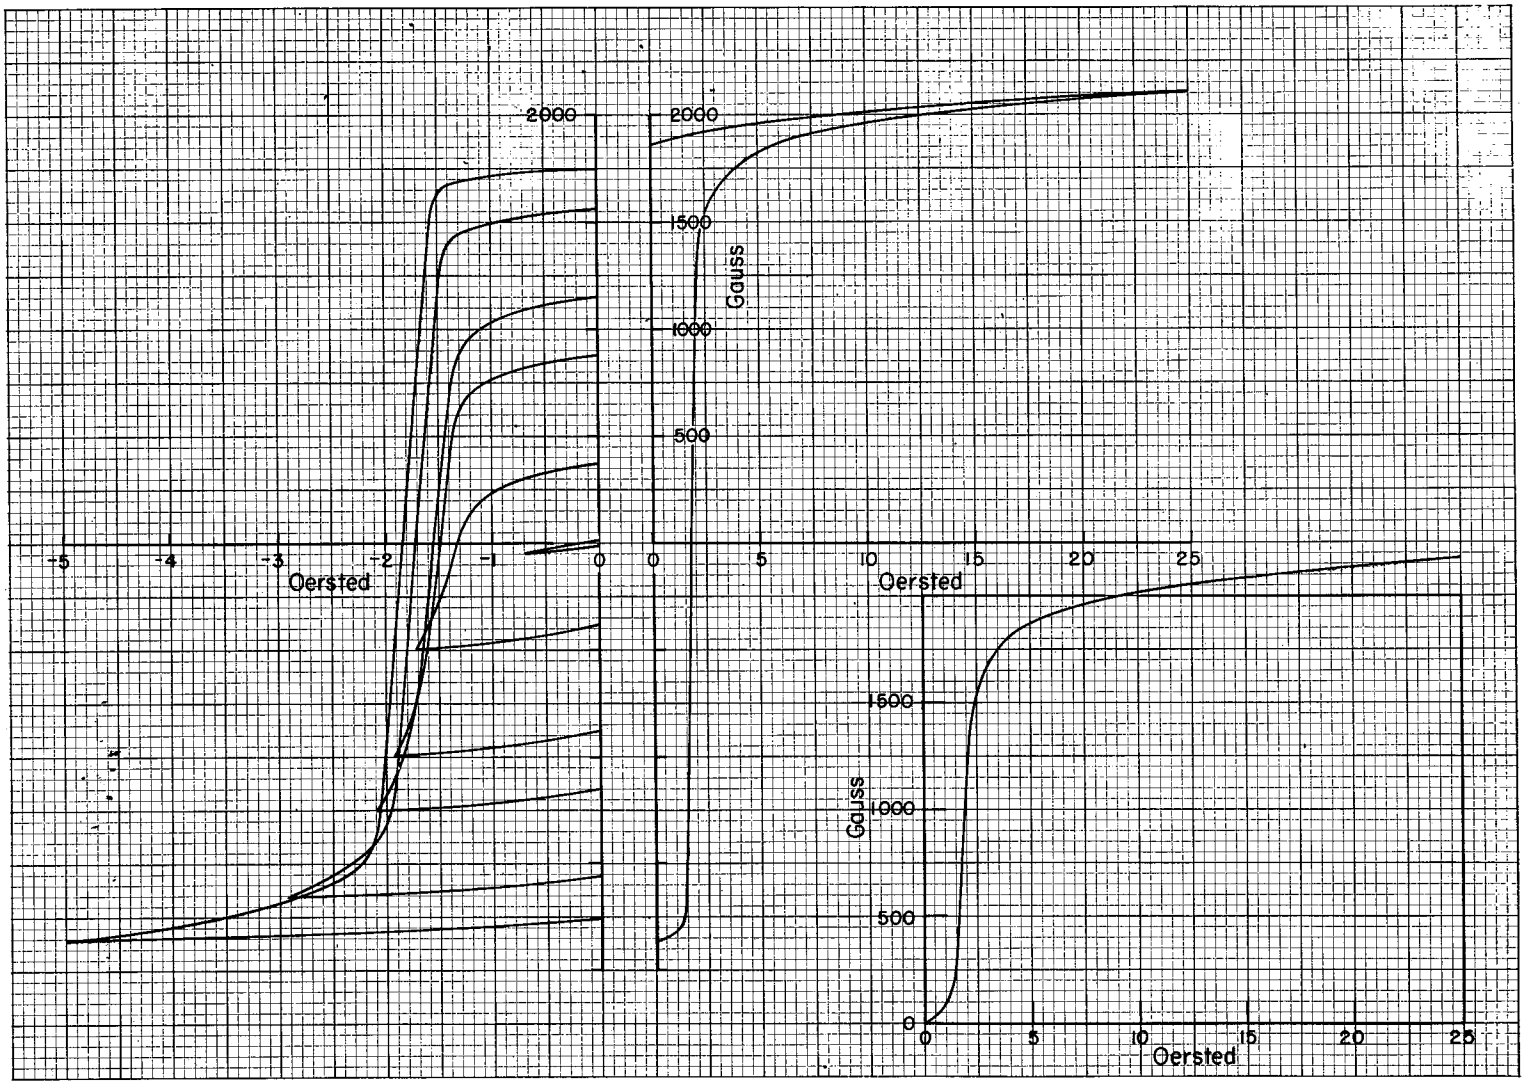

IV B 5. Magnesium-Manganese-Zinc Ferrite Ceramic

$(MgO)_{0.174}(MnO)_{0.209}(ZnO)_{0.221}(Fe_2O_3)_{0.395}$ ($T = 28^{\circ}C$)


M.I.T. Lincoln Lab.

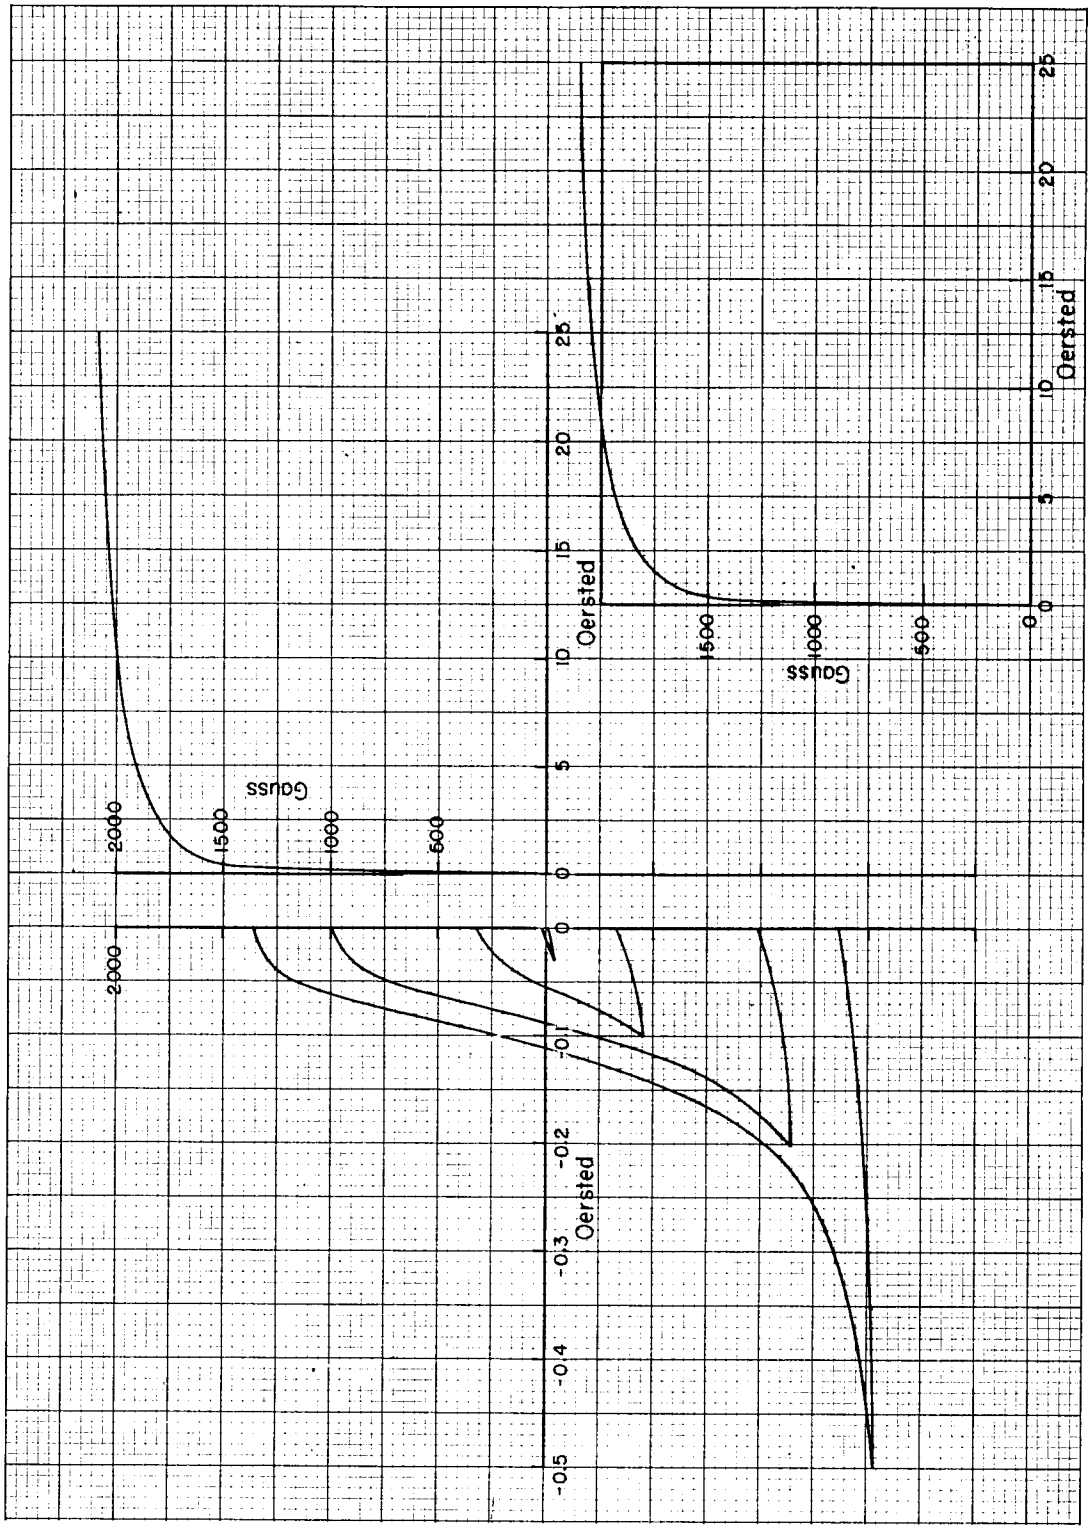

IV B 6. Nickel Ferrite, High Density Ceramic

$NiFe_2O_3$ (T = 27°C)


Lab. Ins. Res.

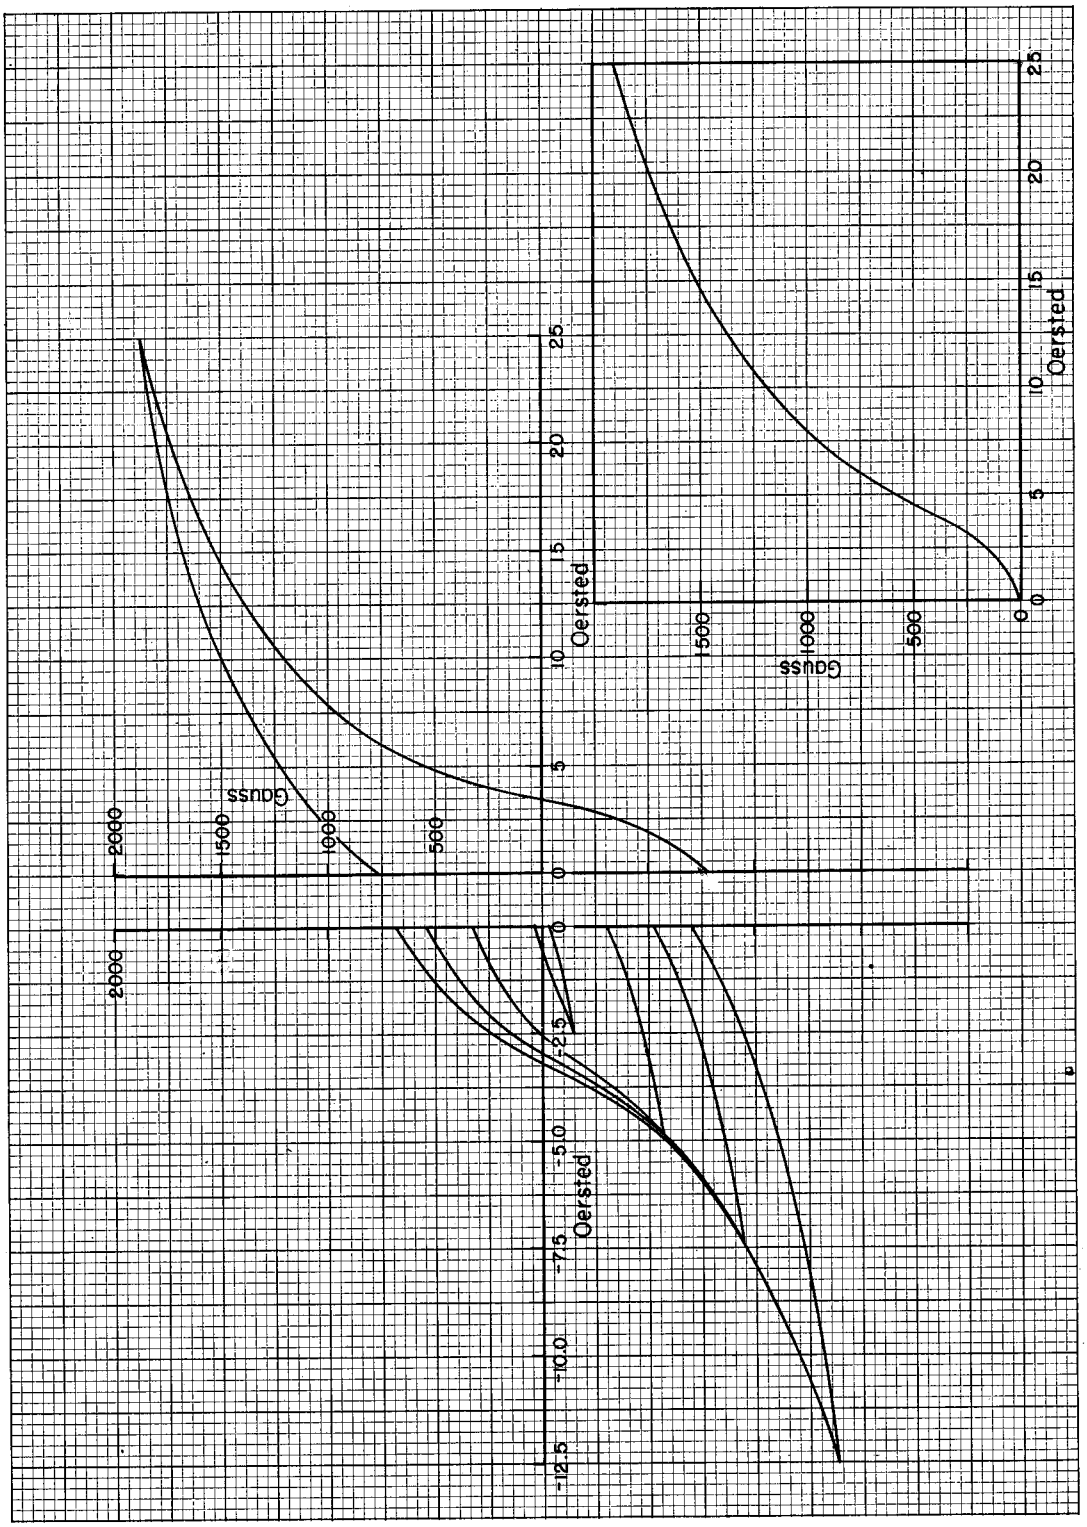

IV B 7. Nickel-Zinc Ferrite, High Density Ceramics

$Ni_{0.9}Zn_{0.1}Fe_2O_4$ ($T = 26^{\circ}C$)


Lab. Ins. Res.

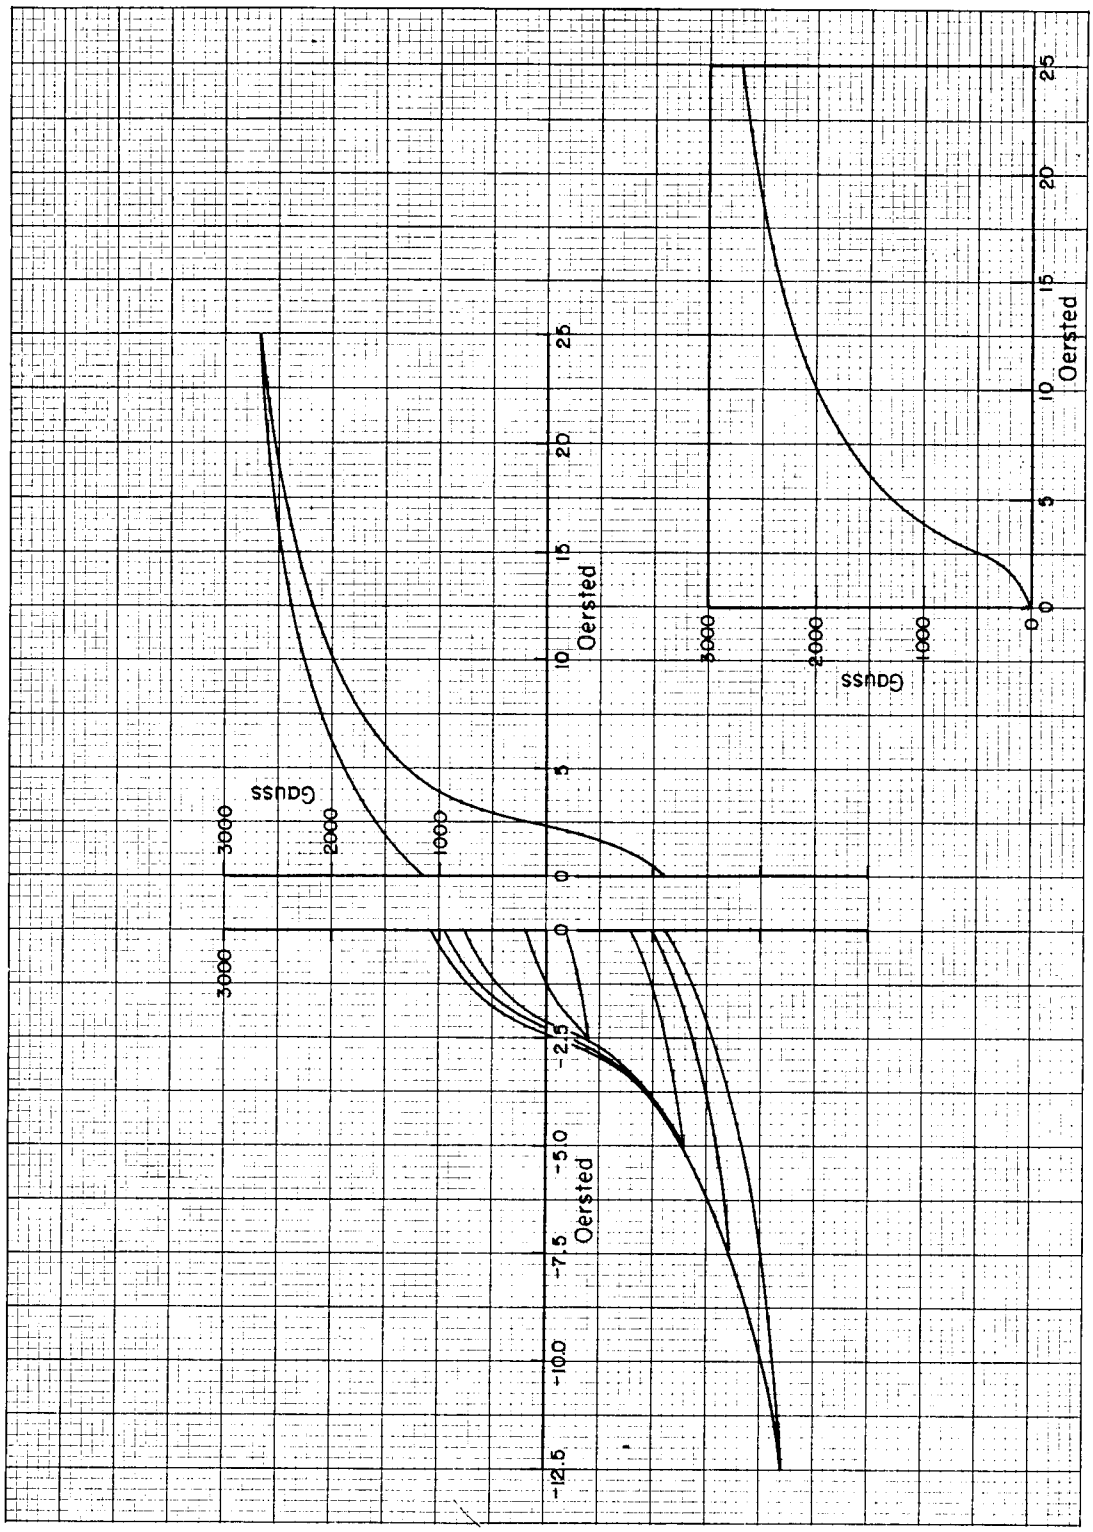

IV B 7. Nickel-Zinc Ferrite, High Density Ceramics

$Ni_{0.8}Zn_{0.2}Fe_2O_4$ (T = 26°C)


Lab. Ins. Res.

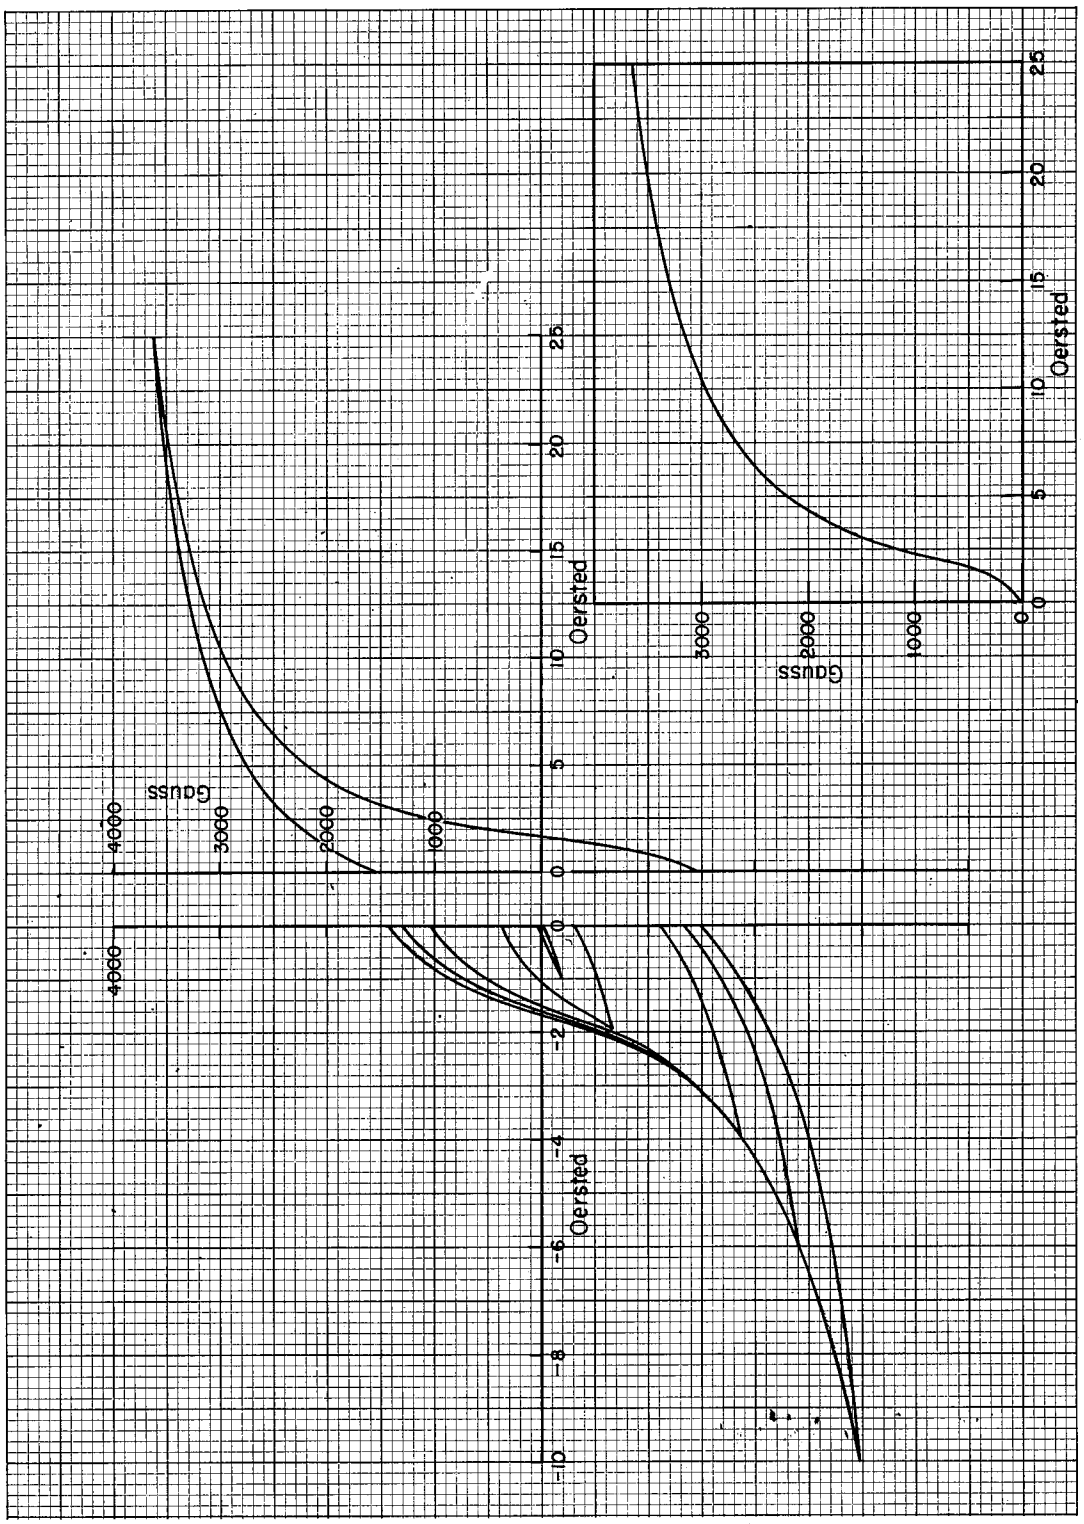

IV B 7. Nickel-Zinc Ferrite, High Density Ceramics

$Ni_{0.7}Zn_{0.3}Fe_2O_4$ (T = 26°C)


Lab. Ins. Res.

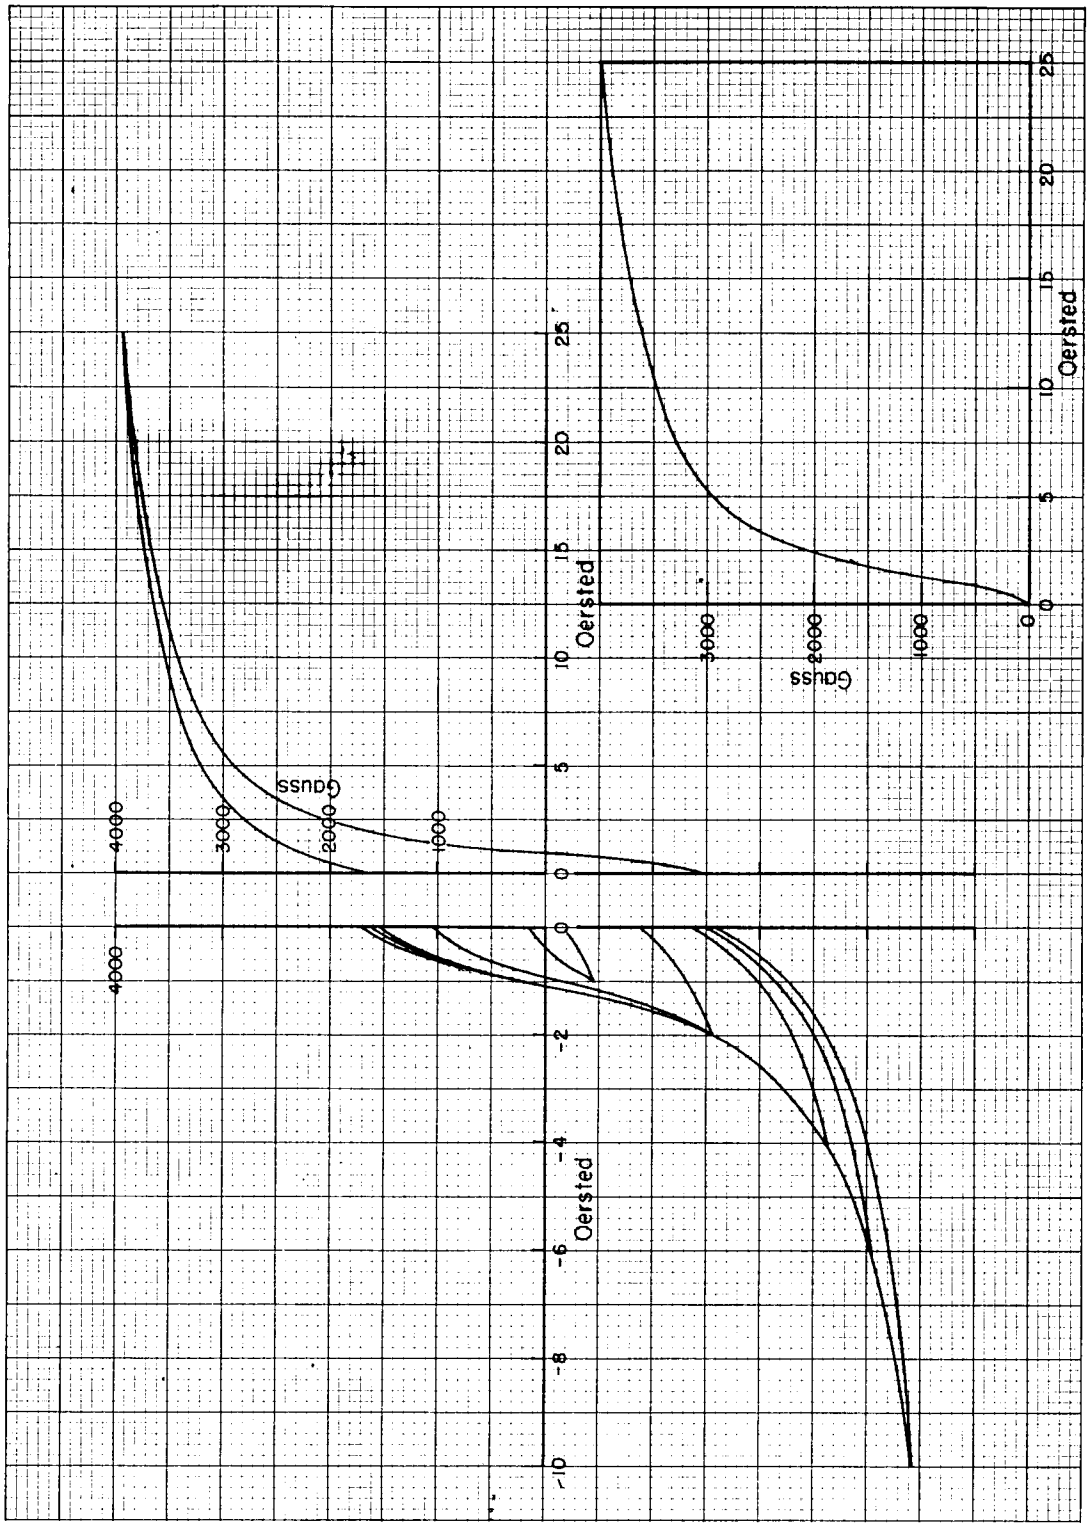

IV B 7. Nickel-Zinc Ferrite, High Density Ceramics

$Ni_{0.6}Zn_{0.4}Fe_2O_4$ ($T = 26^{\circ}C$)


Lab. Ins. Res.

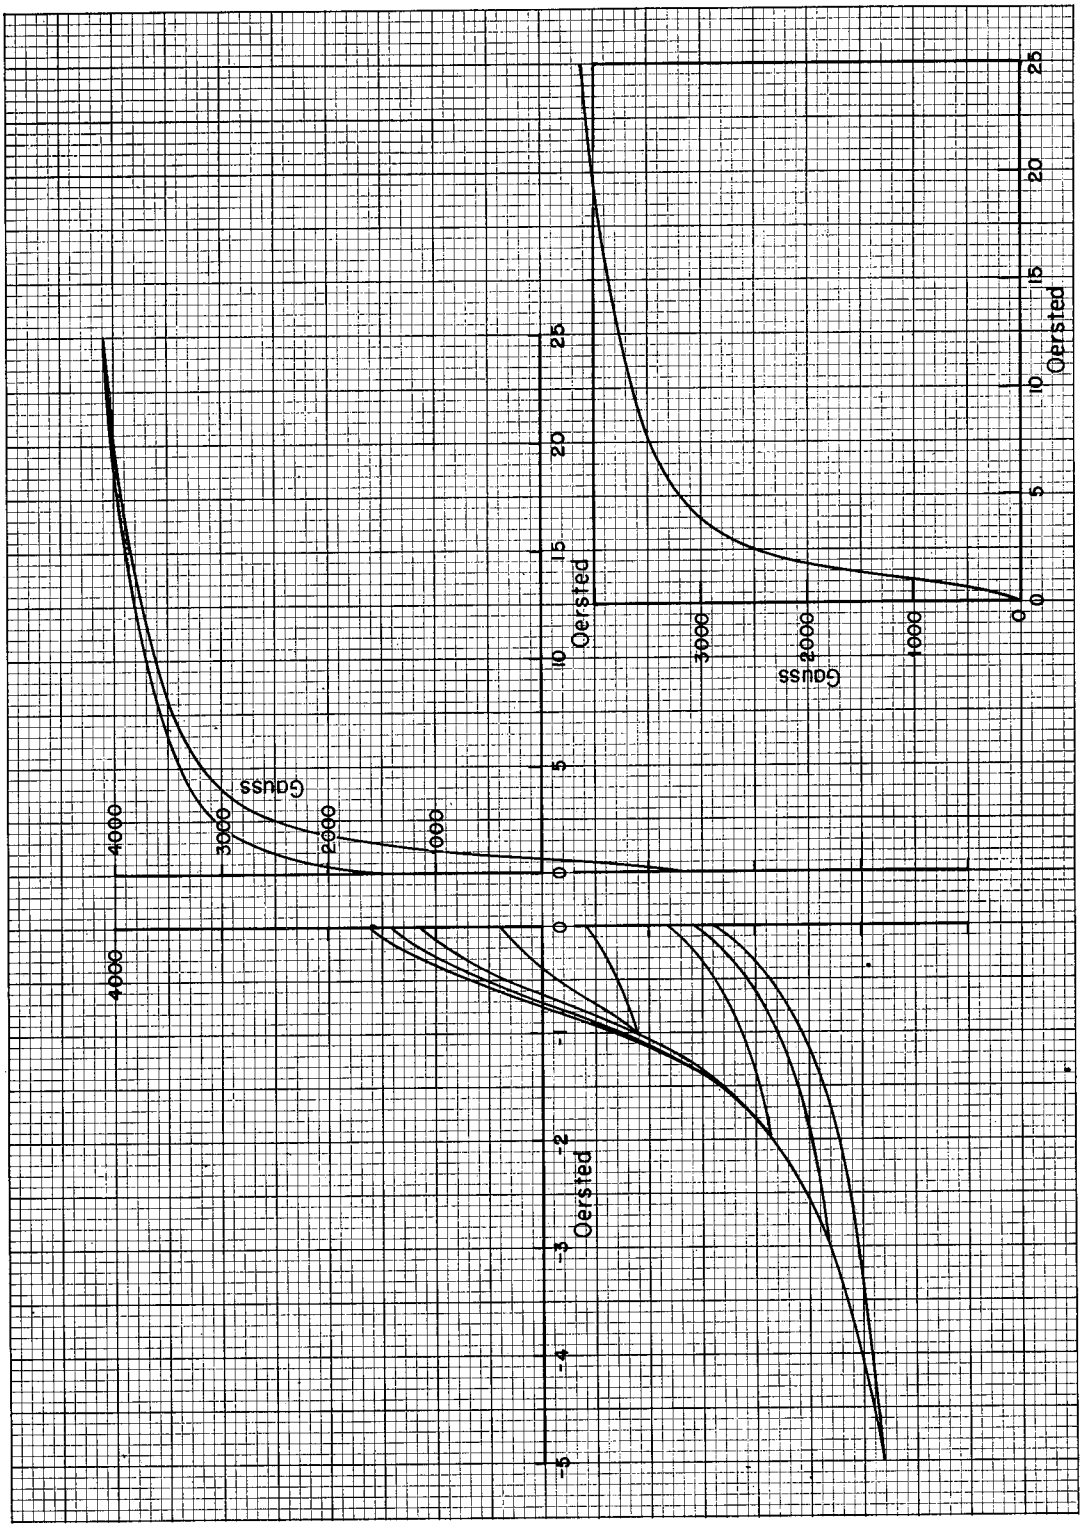

IV B 7. Nickel-Zinc Ferrite, High Density Ceramics

$Ni_{0.5}Zn_{0.5}Fe_2O_4$ (T = 26°C)


Lab. Ins. Res.

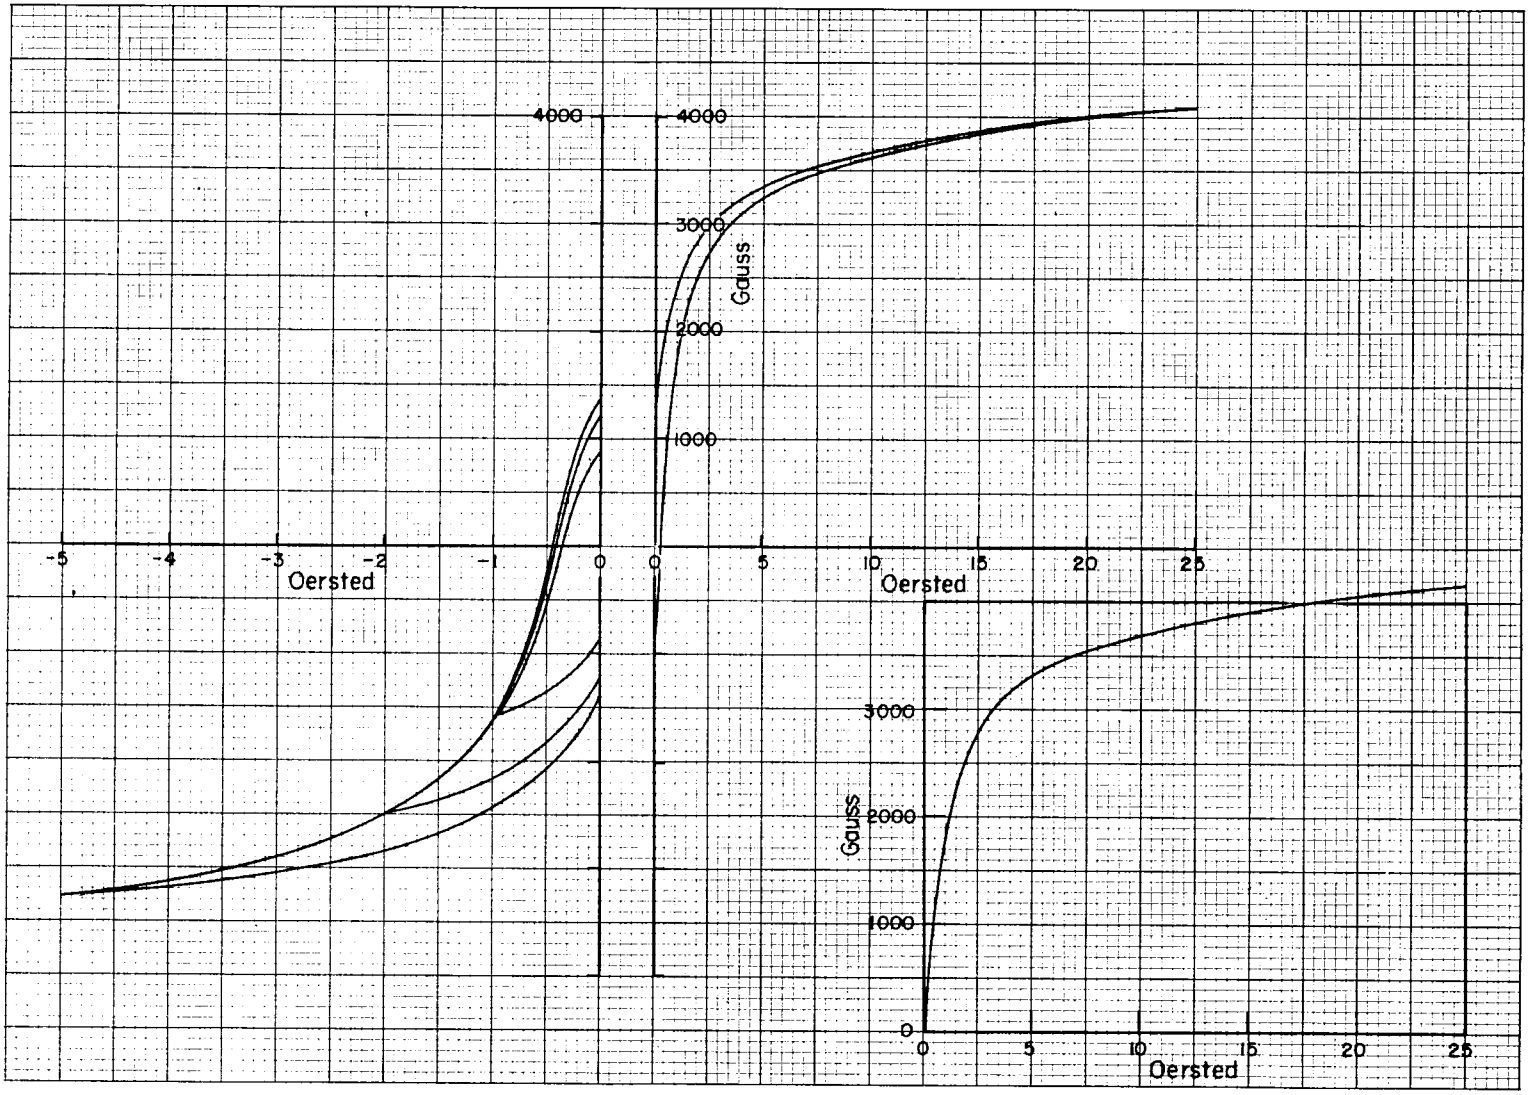

IV B 7. Nickel-Zinc Ferrite, High Density Ceramics

$Ni_{0.4}Zn_{0.6}Fe_2O_4$ (T = 26°C)


Lab. Ins. Res.

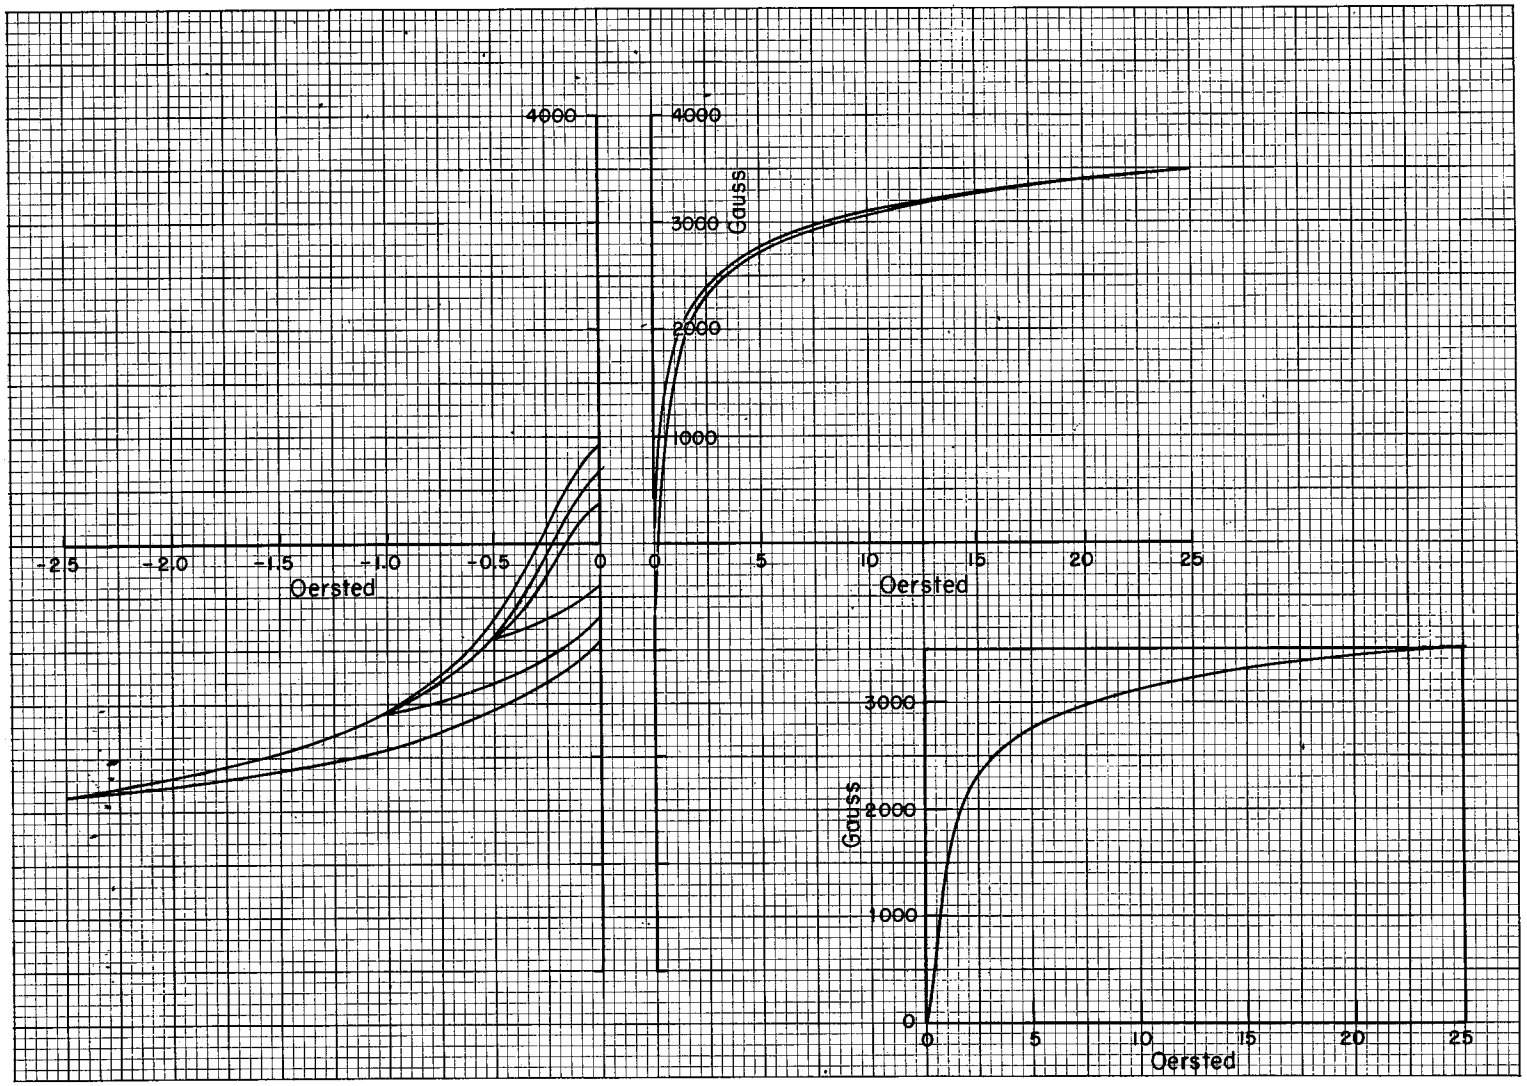

IV B 7. Nickel-Zinc Ferrite, High Density Ceramics

$Ni_{0.3}Zn_{0.7}Fe_2O_4$ (T = 29°C)


Lab. Ins. Res.

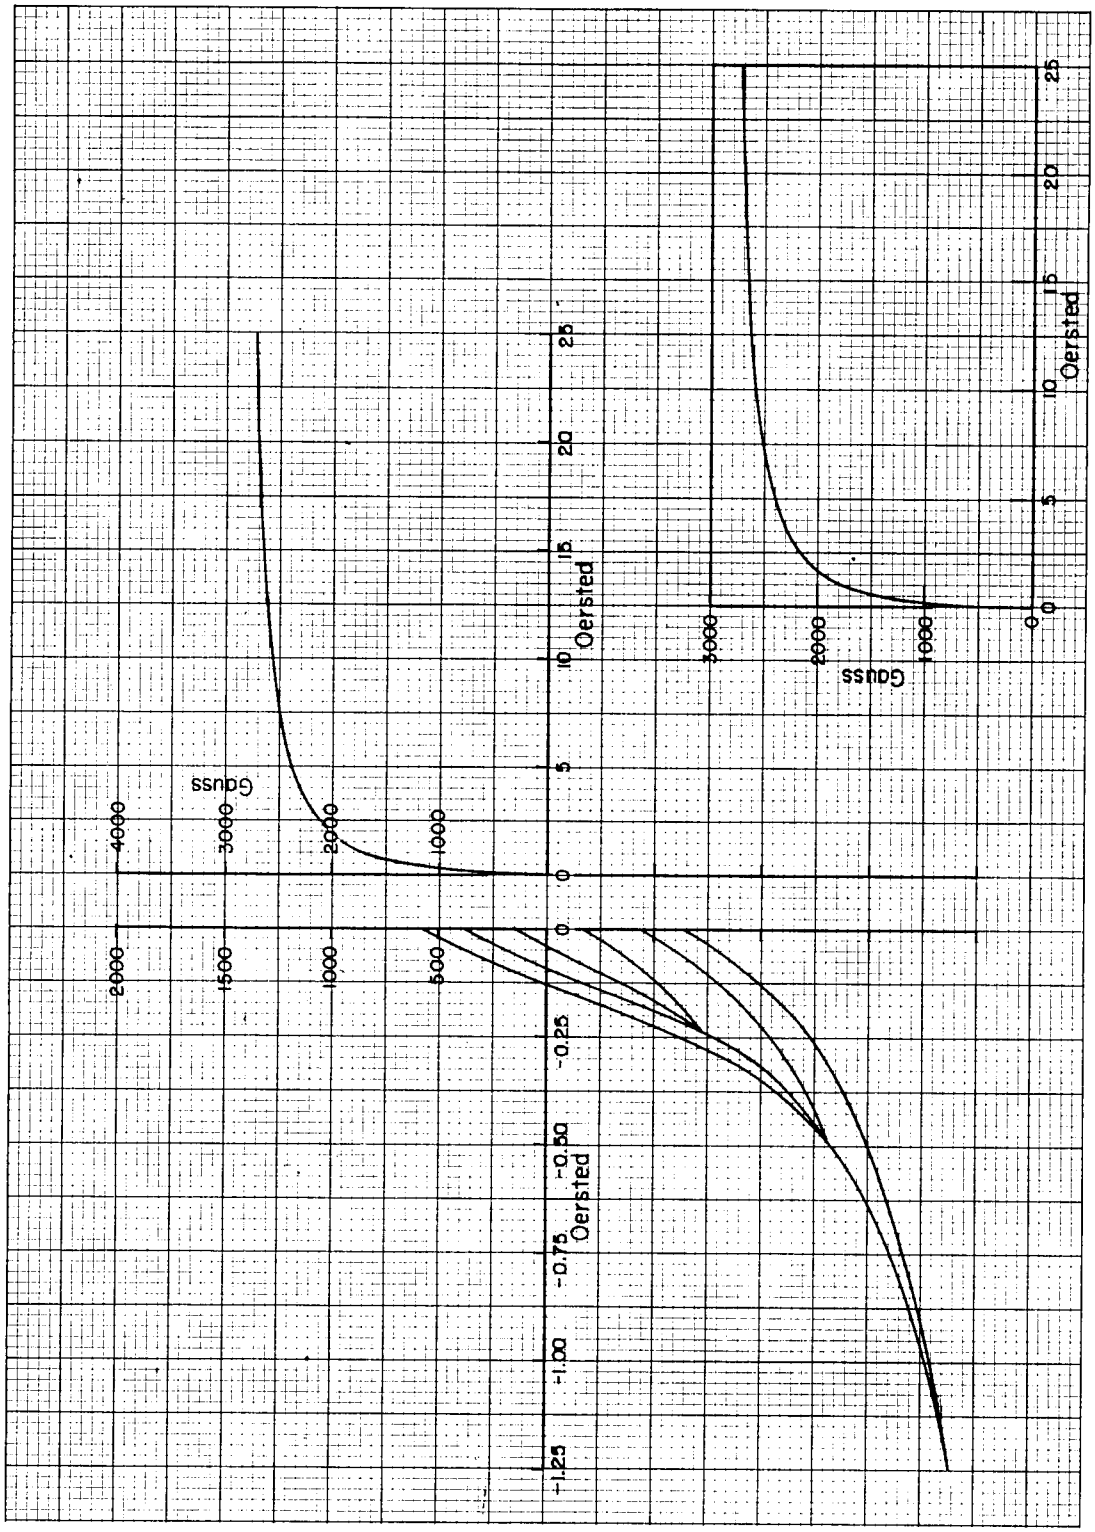

IV B 8. Commercial Ferrite Ceramics

"Ferramic" A (T = 29°C)


General Ceramics

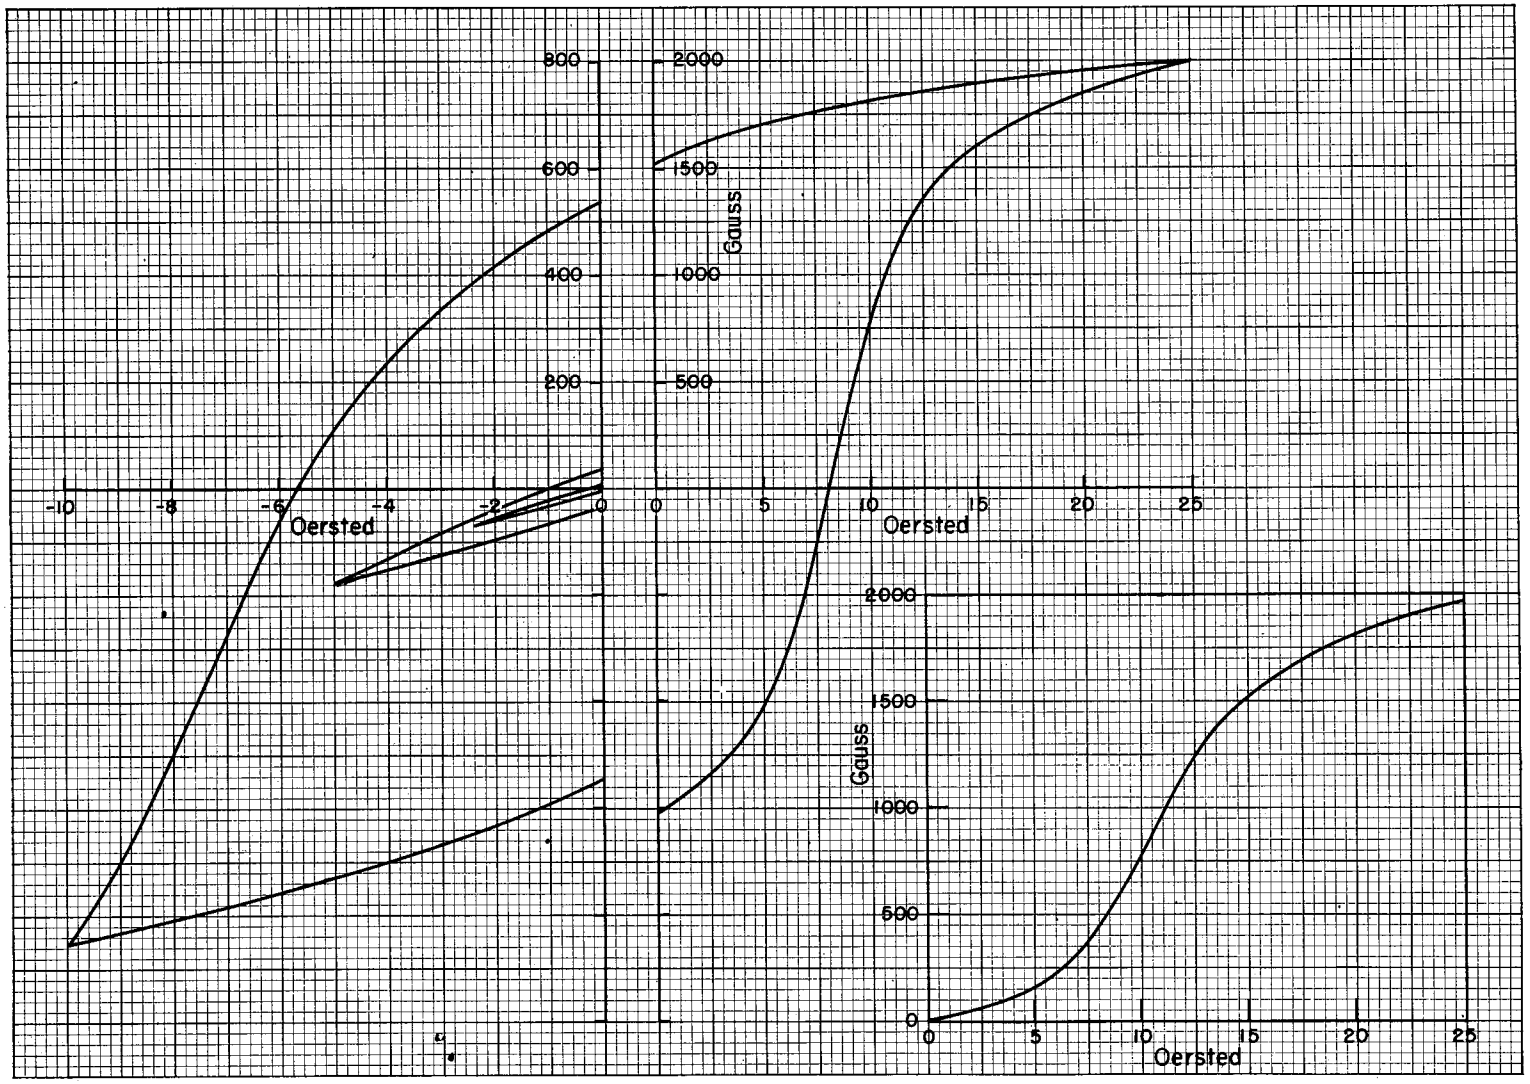

IV B 8. Commercial Ferrite Ceramics

General Ceramics


"Ferramic" B (T = 25°C)

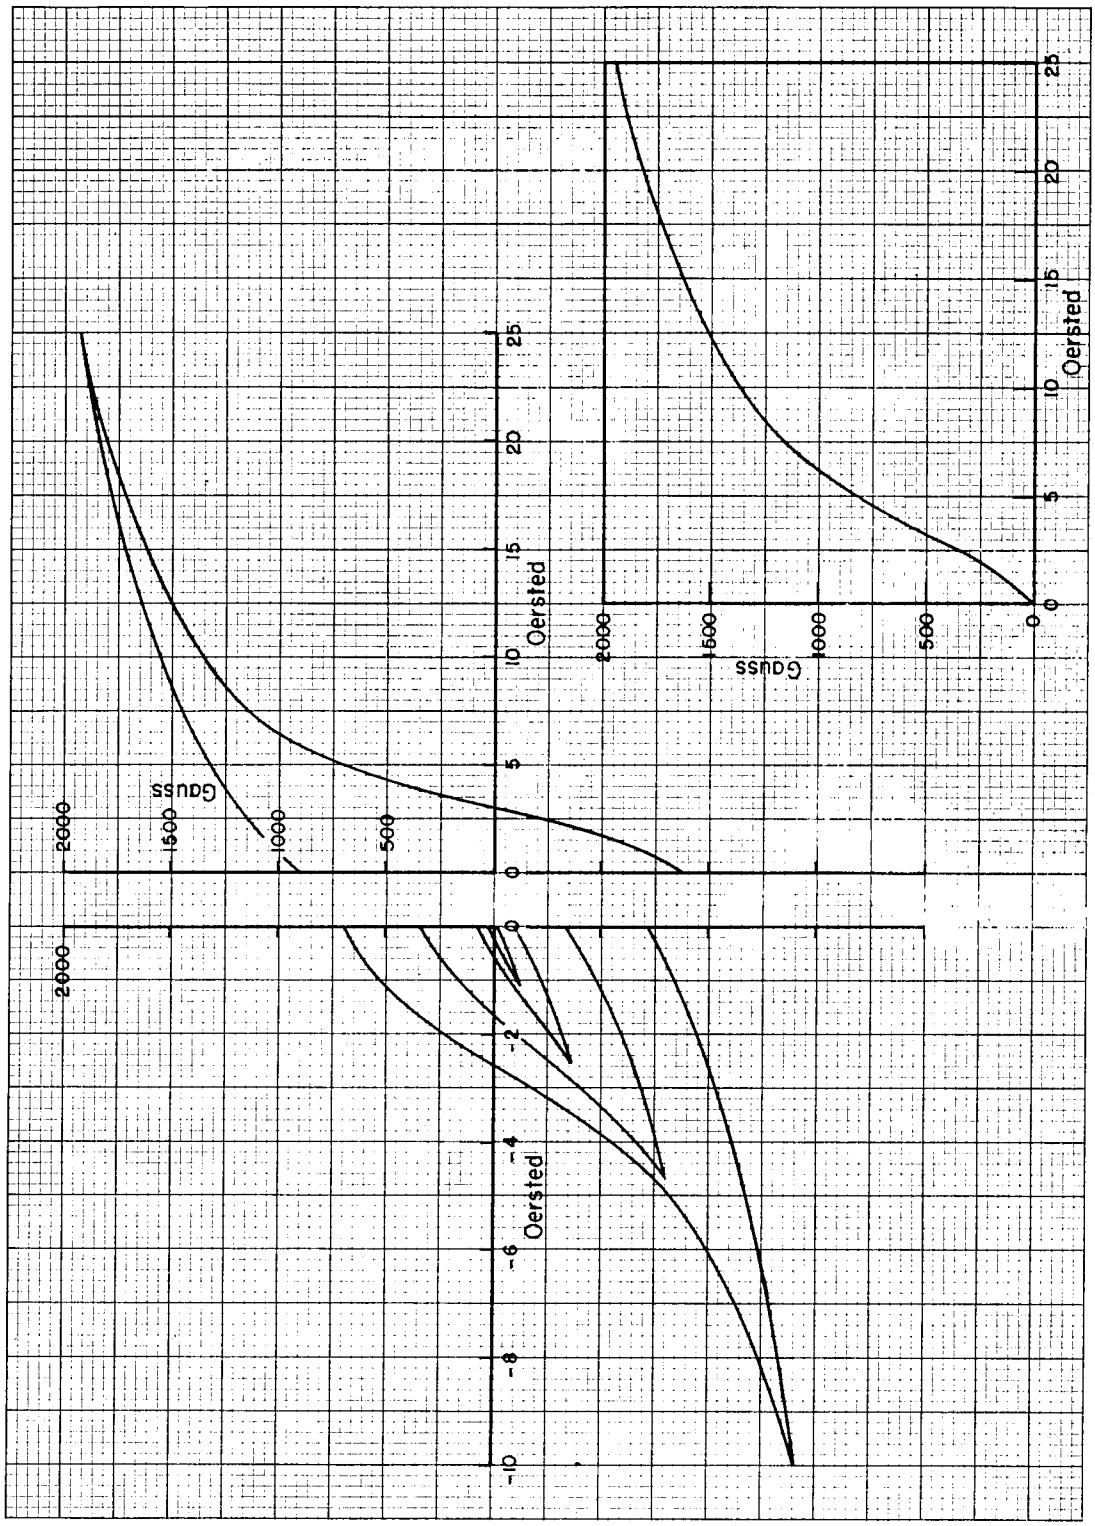

IV B 8. Commercial Ferrite Ceramics

"Ferramic" C


General Ceramics

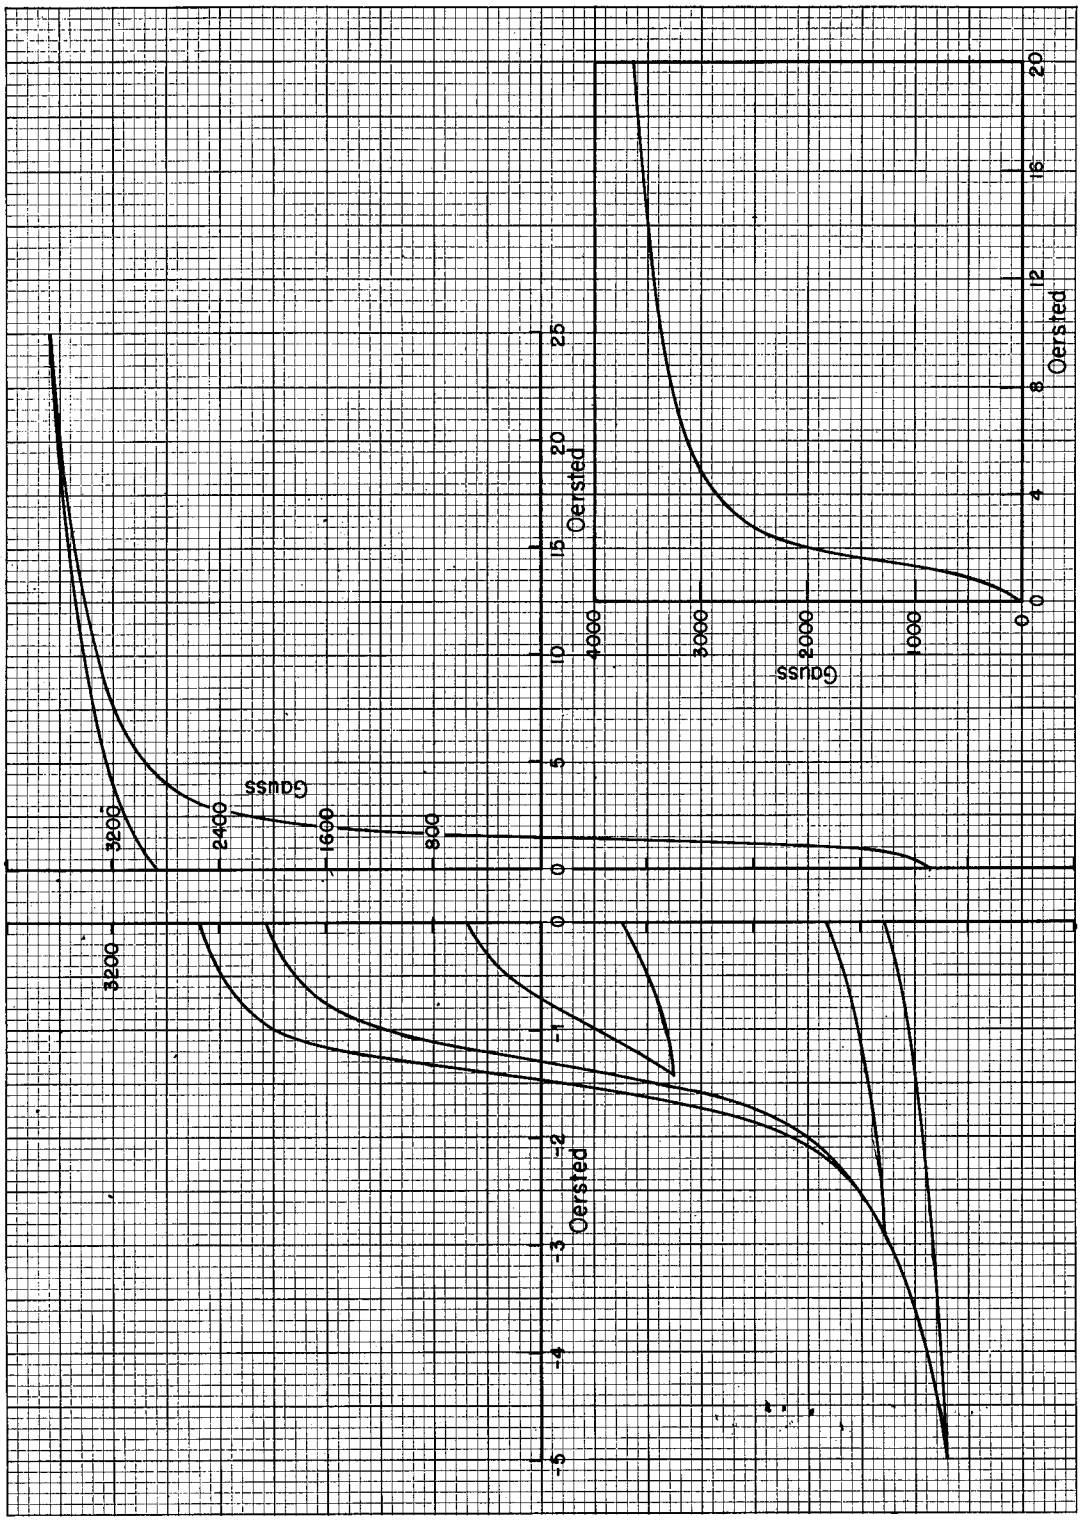

IV B 8. Commercial Ferrite Ceramics

"Ferramic" D


General Ceramics

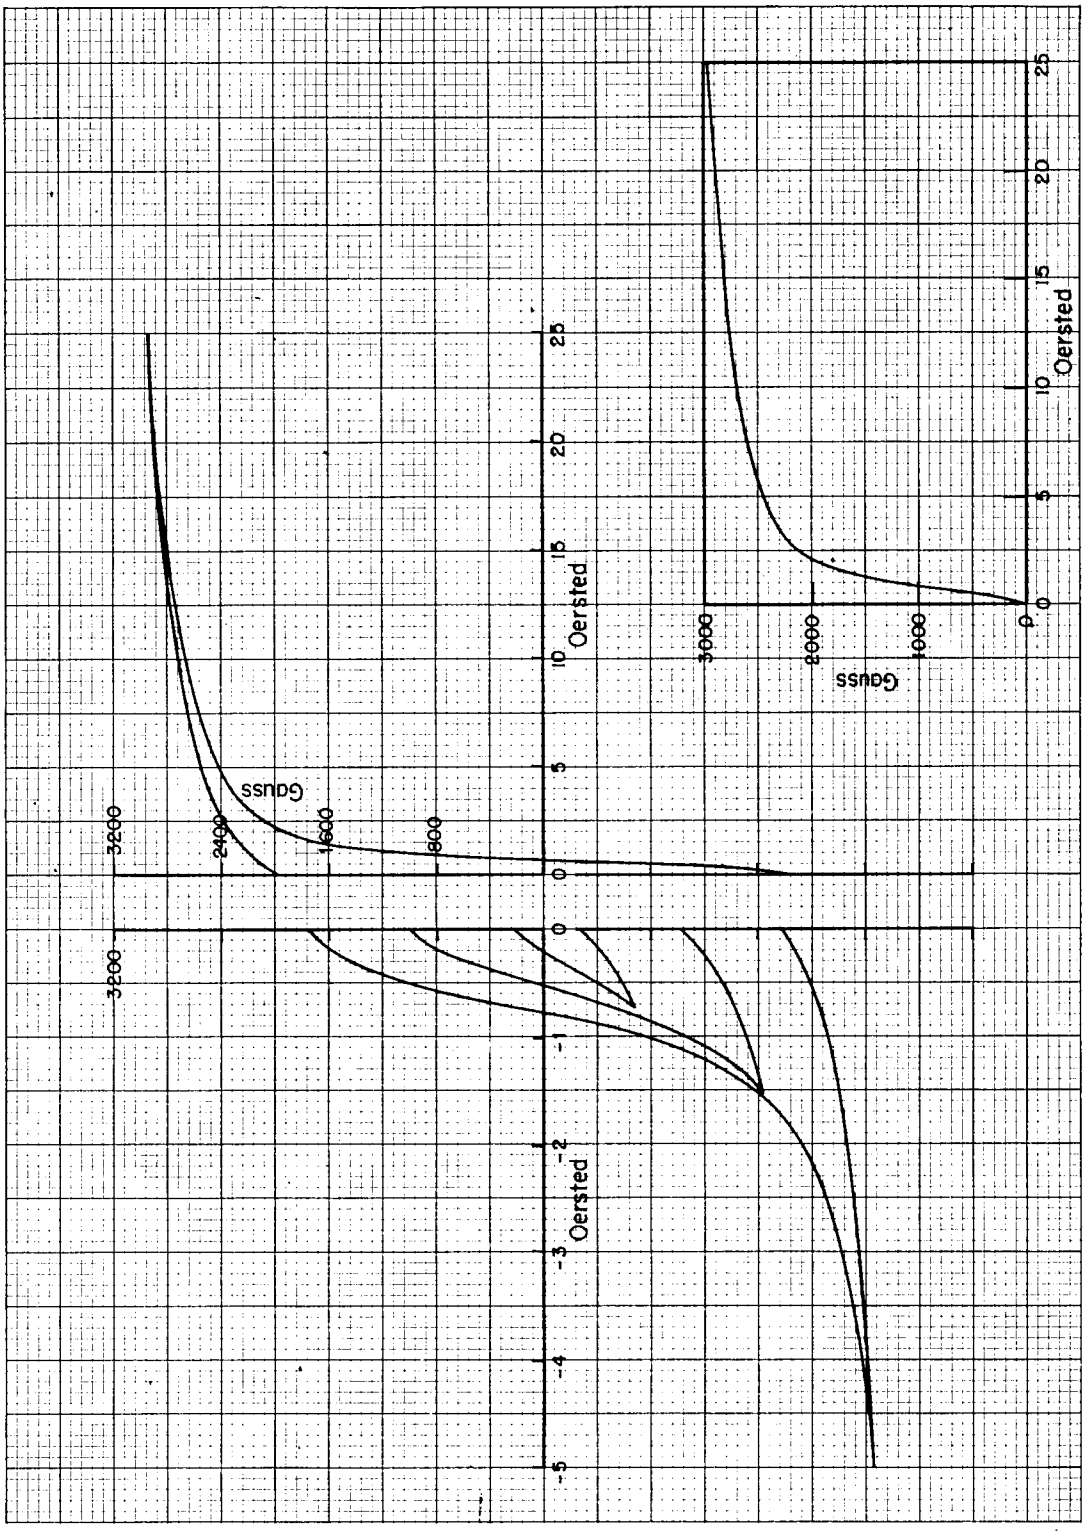

IV B 8. Commercial Ferrite Ceramics

General Ceramics


"Ferramic" E (T = 24°C)

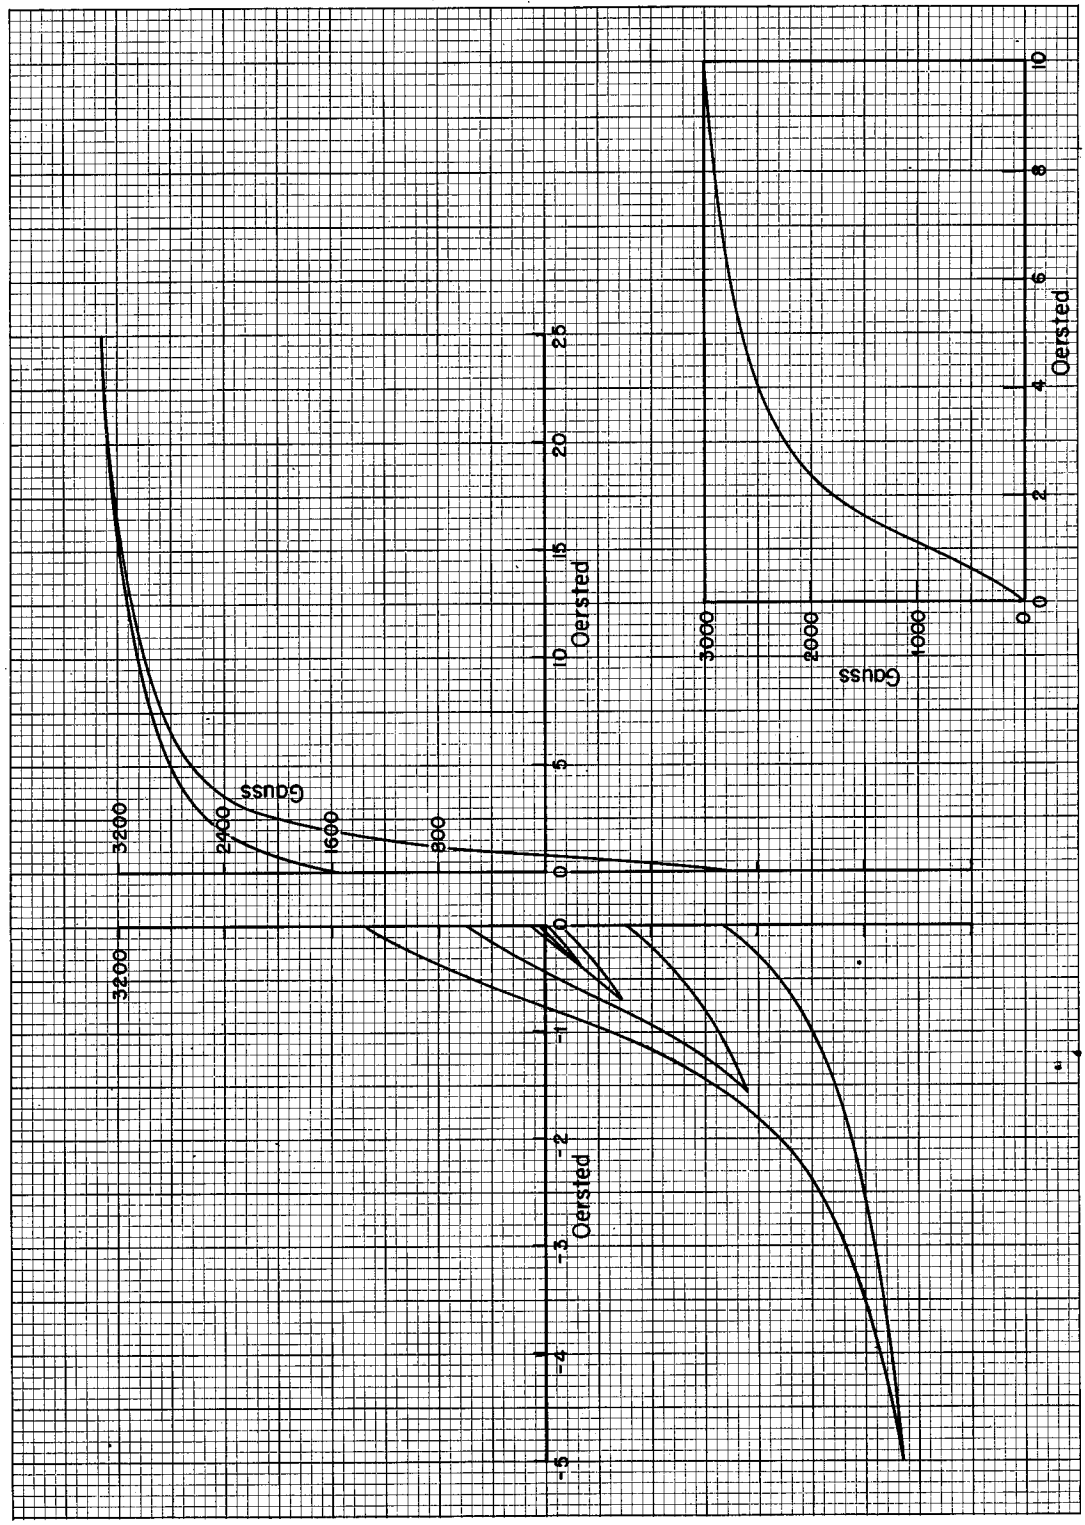

IV B 8. Commercial Ferrite Ceramics

"Ferramic" G (T = 25°C)


General Ceramics

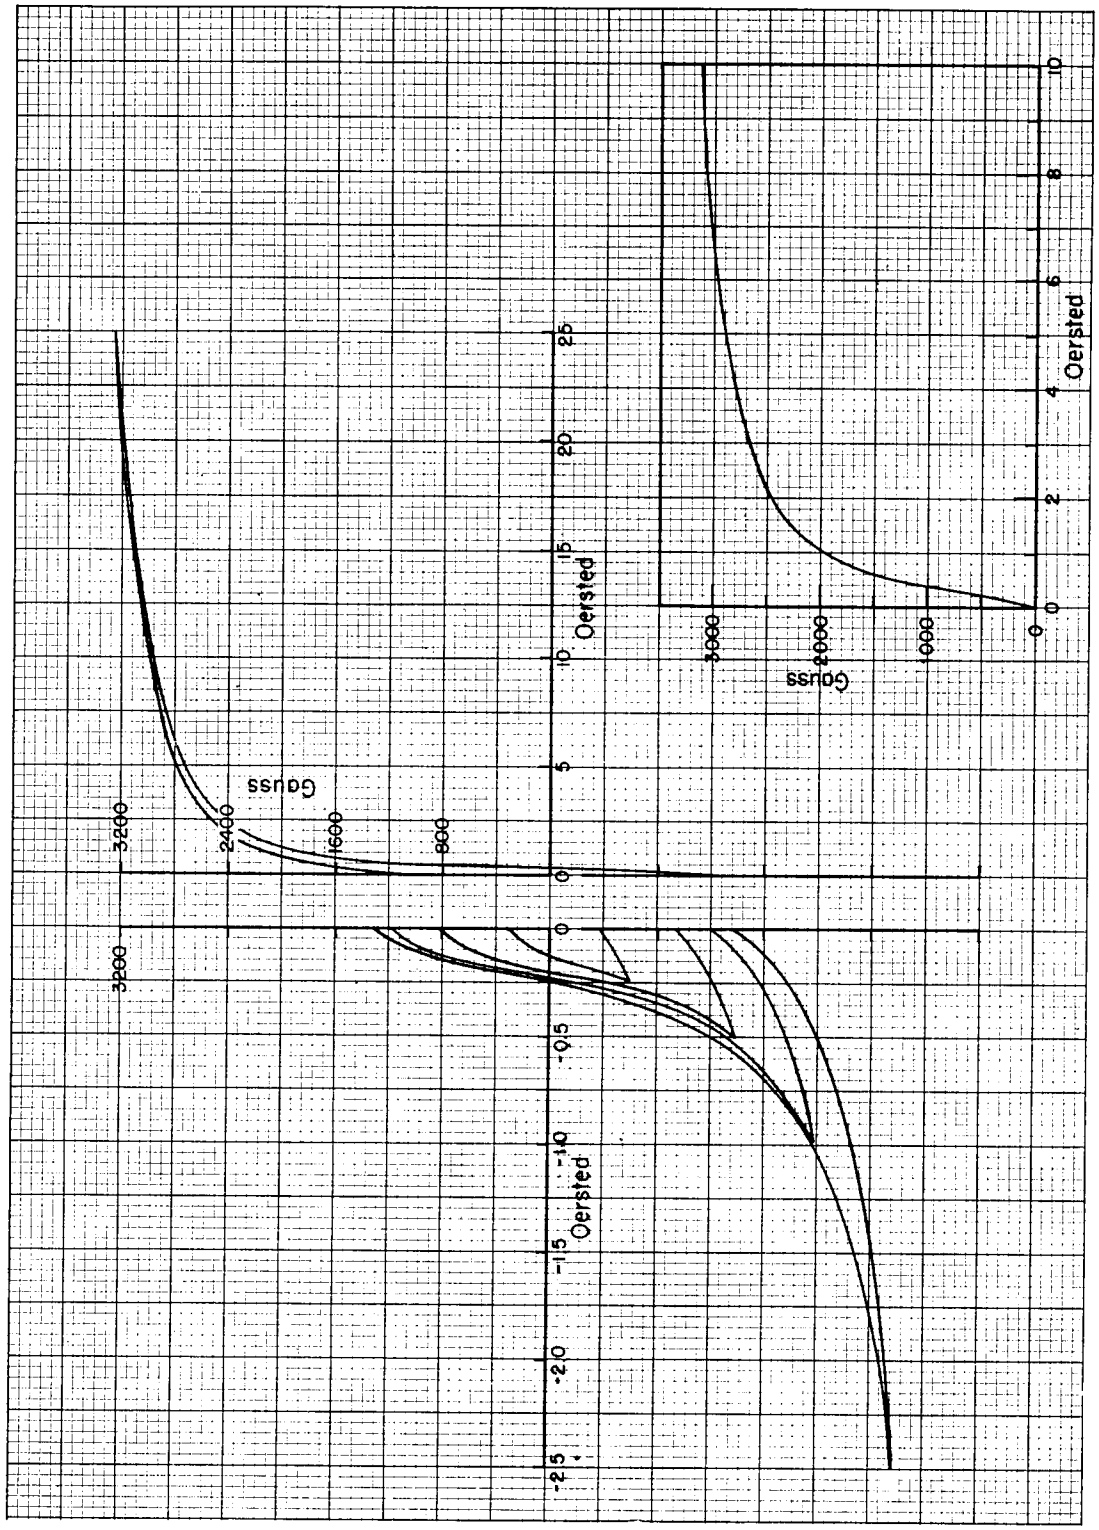

IV B 8. Commercial Ferrite Ceramics


"Ferramic" H (T = 26.5°C)

General Ceramics

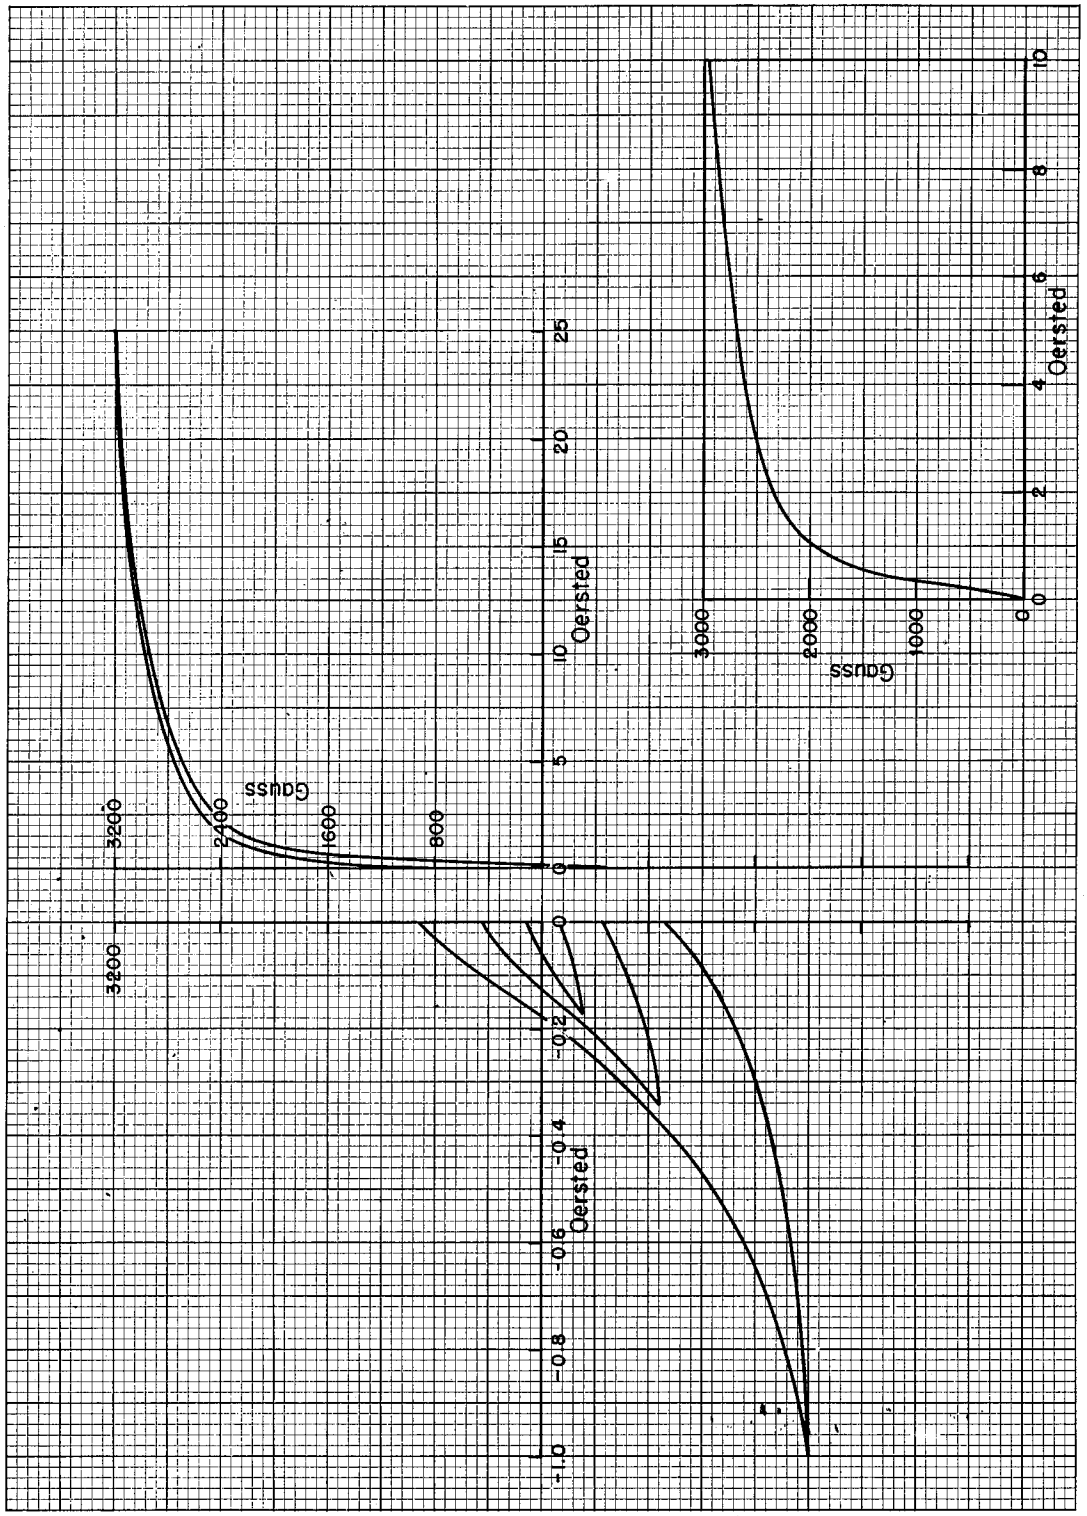


"Ferramic" H-1 (T = 27°C)

General Ceramics

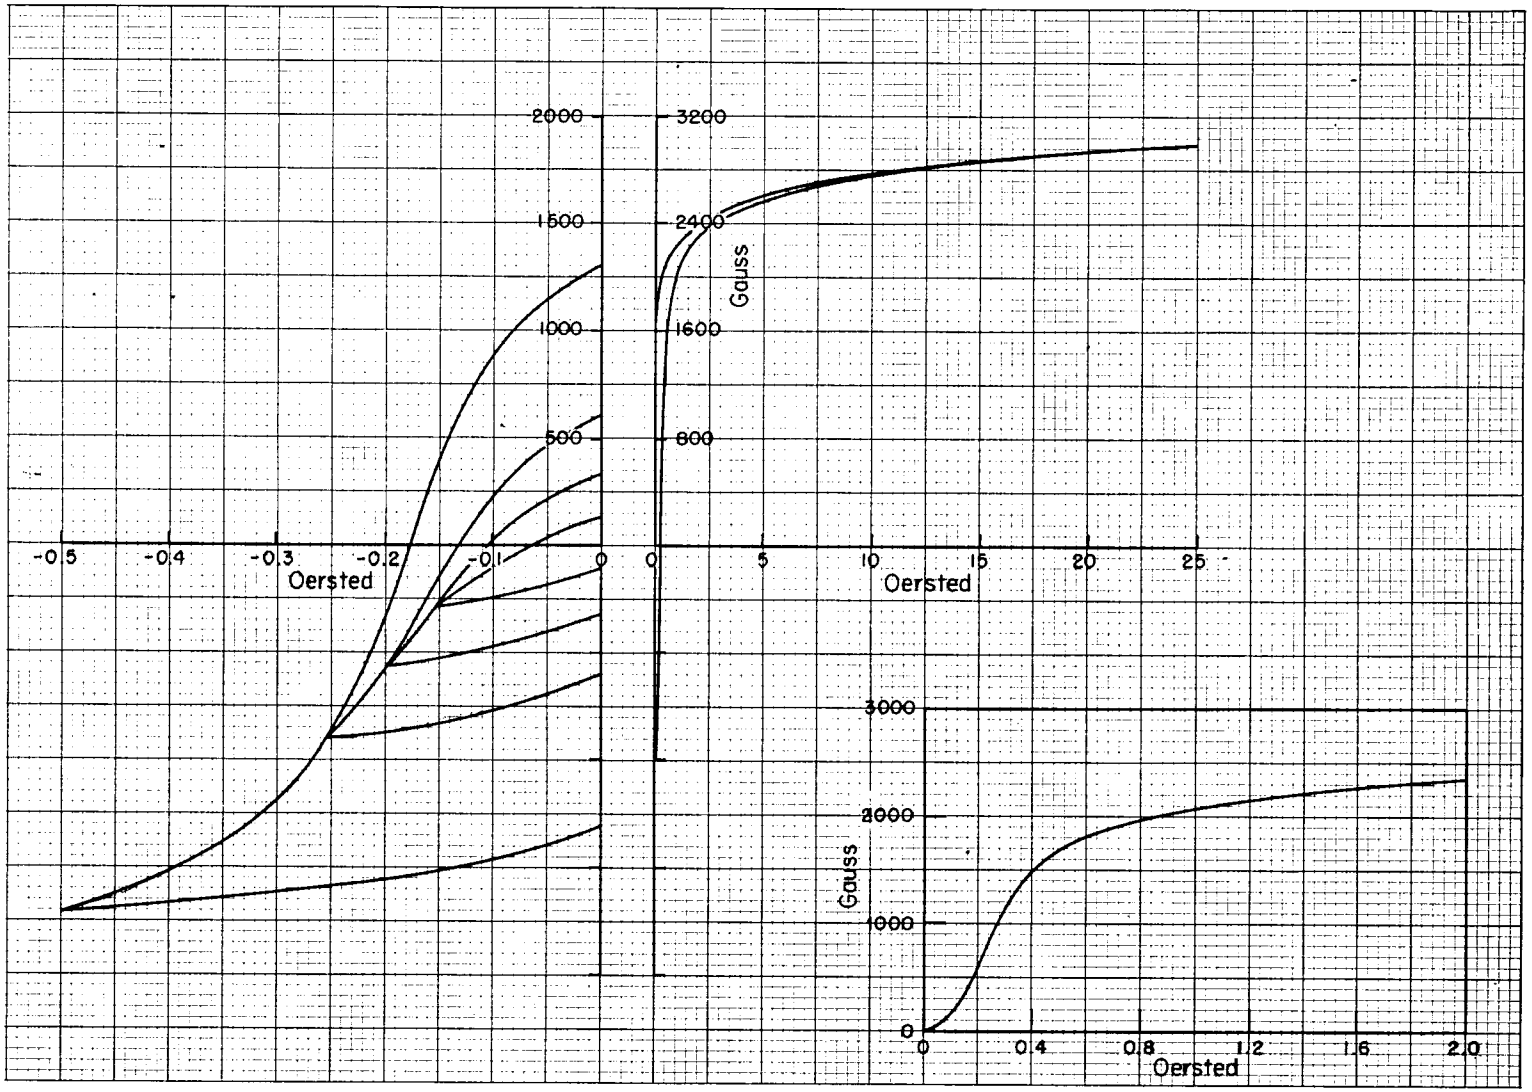

"Ferramic" $\widetilde{J}$ ($T = 25^{\circ}C$)


General Ceramics

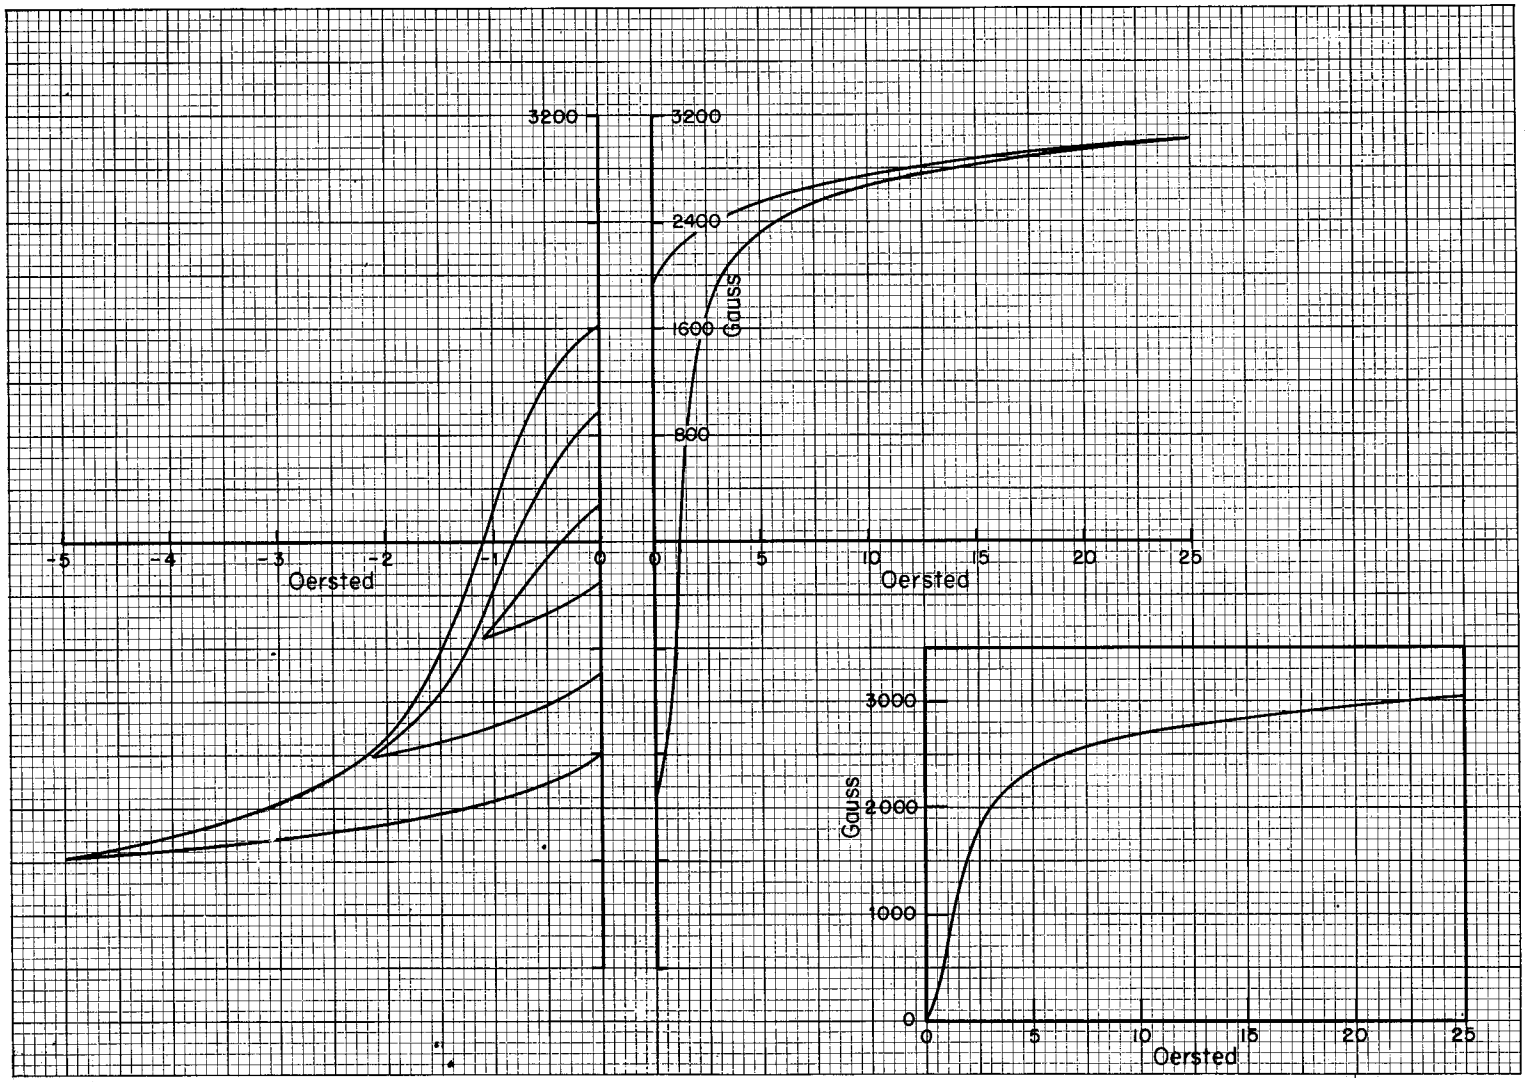

IV B 8. Commercial Ferrite Ceramics

General Ceramics


"Ferramic" N (T = 27°C)

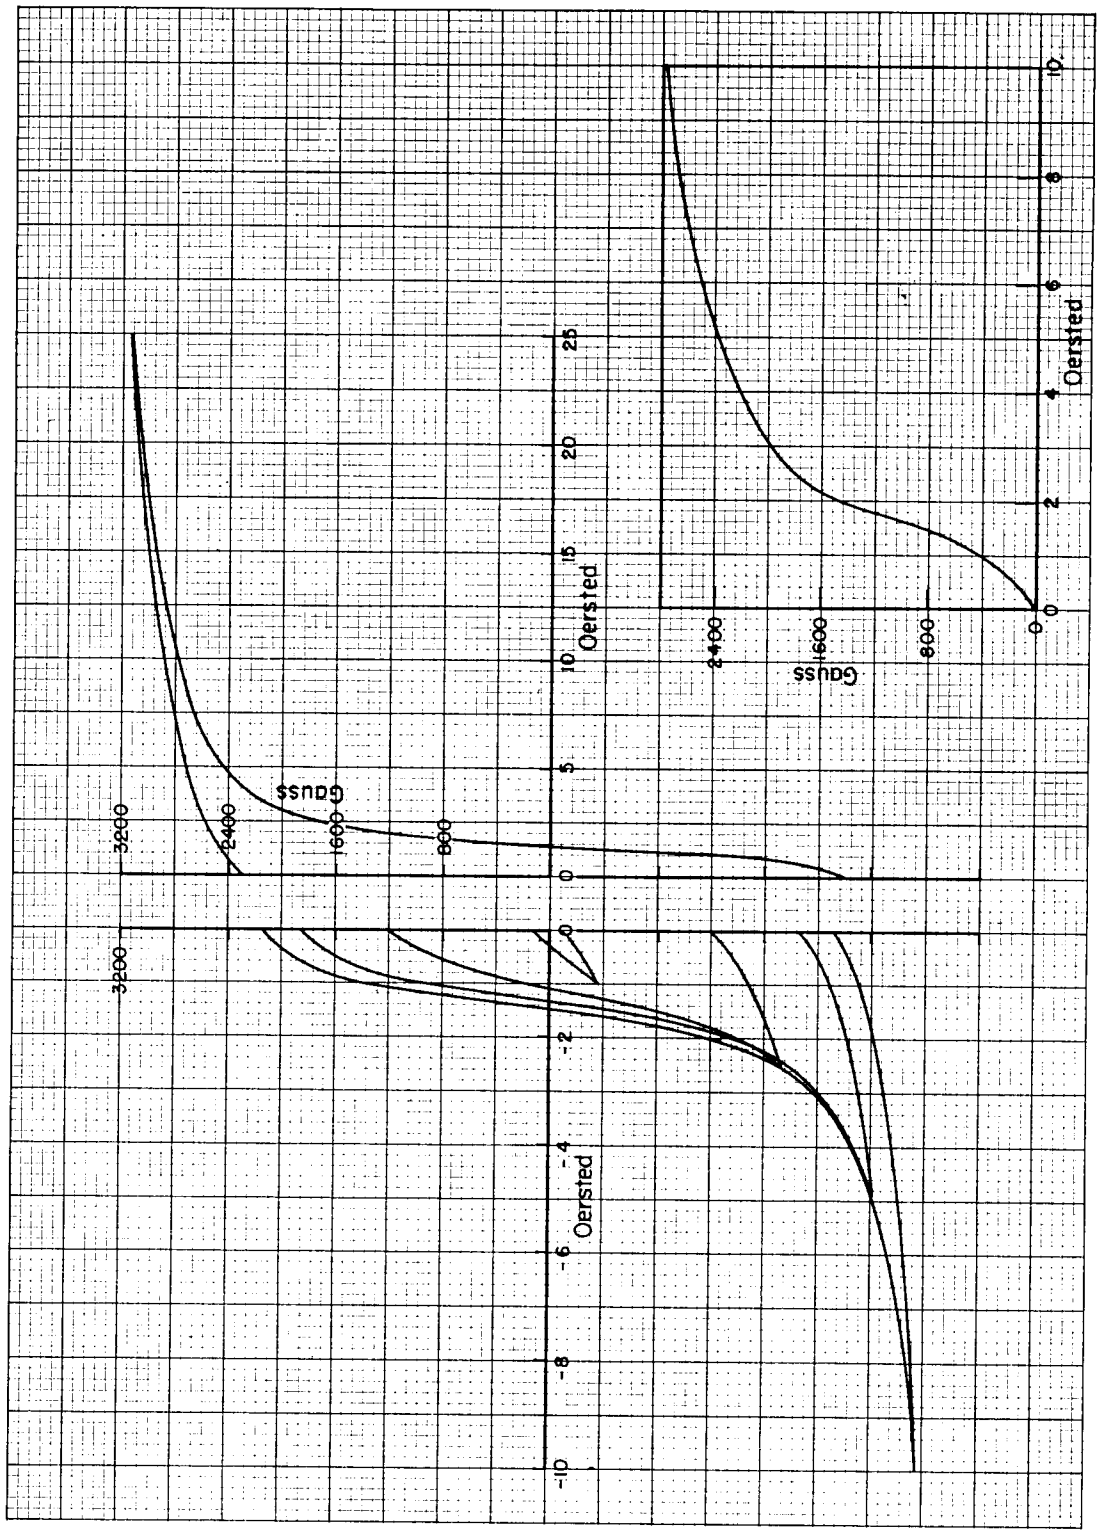

IV B 8. Commercial Ferrite Ceramics

"Ferramic" Q


General Ceramics

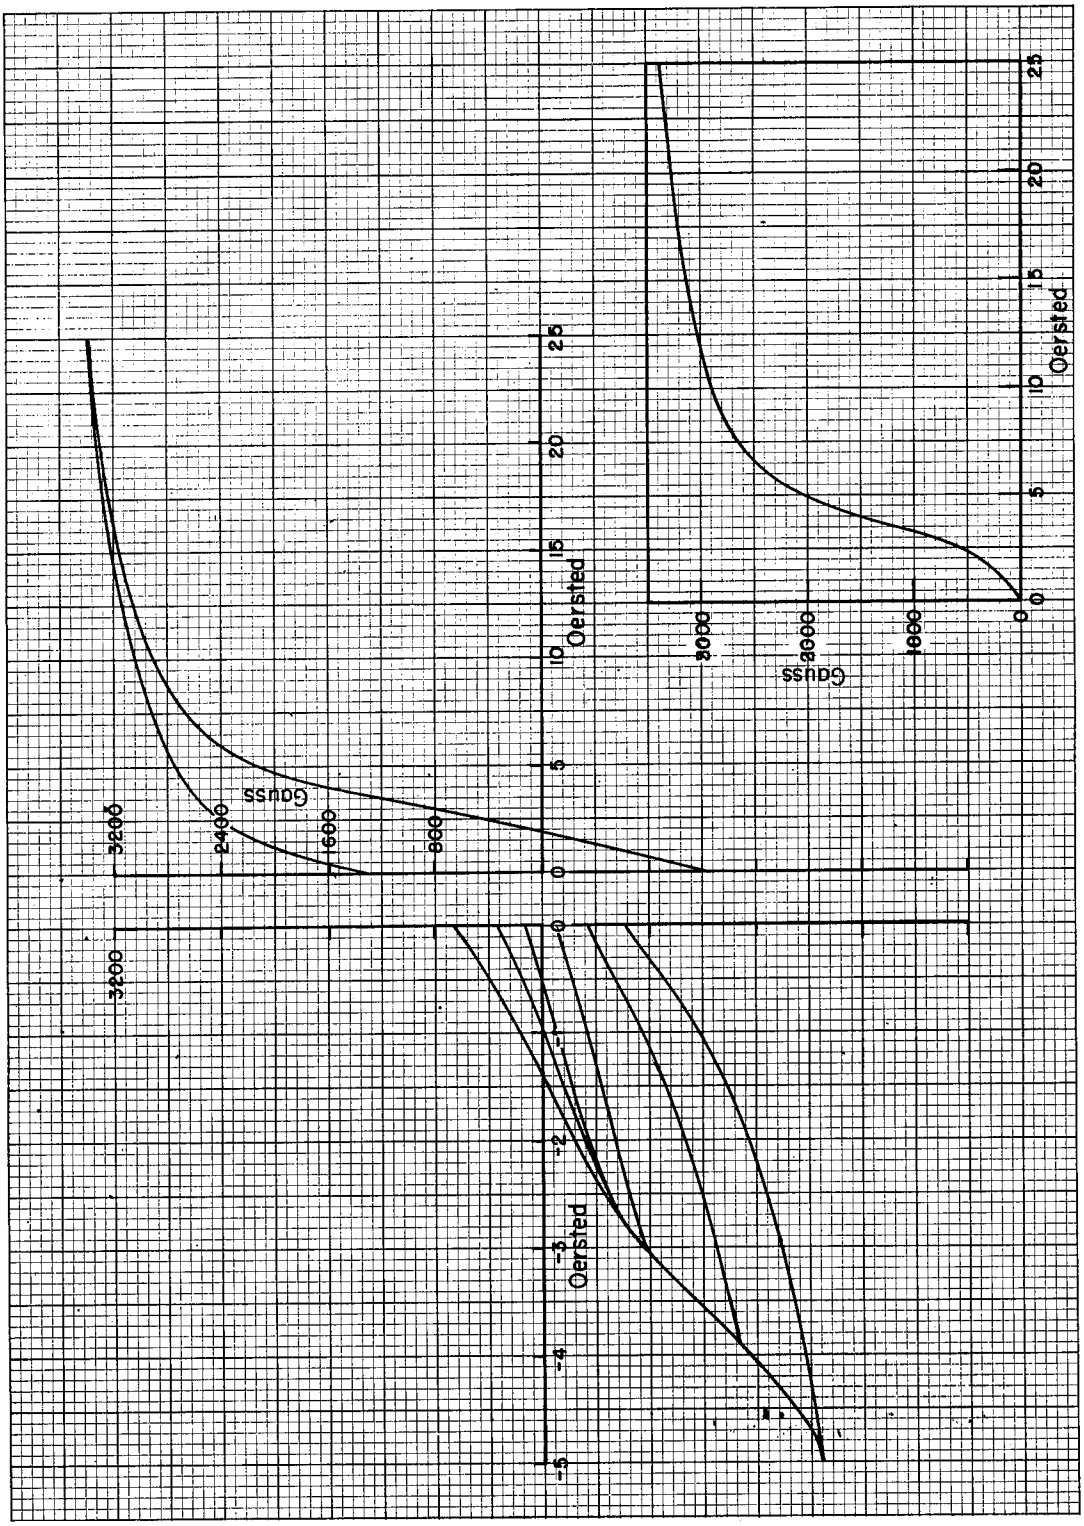

IV B 8. Commercial Ferrite Ceramics

"Ferramic" MF 874 (T = 22°C)


General Ceramics

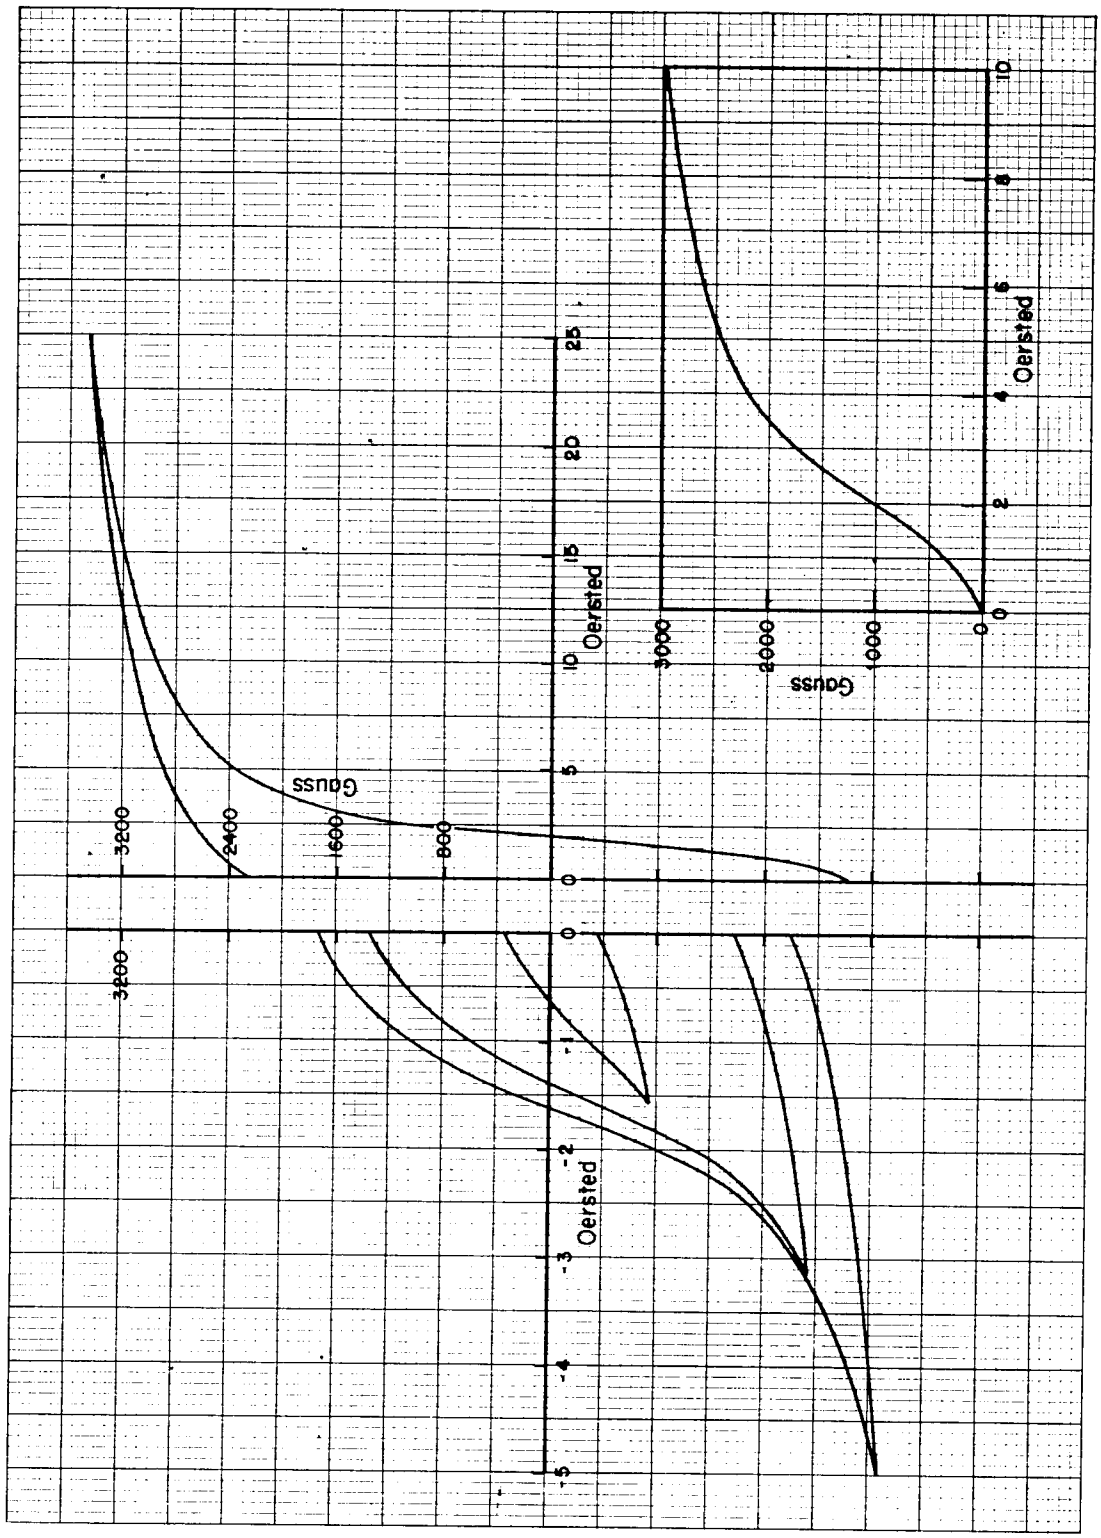

IV B 8. Commercial Ferrite Ceramics

"Ferramic" 1326 B (T = 24°C)


General Ceramics

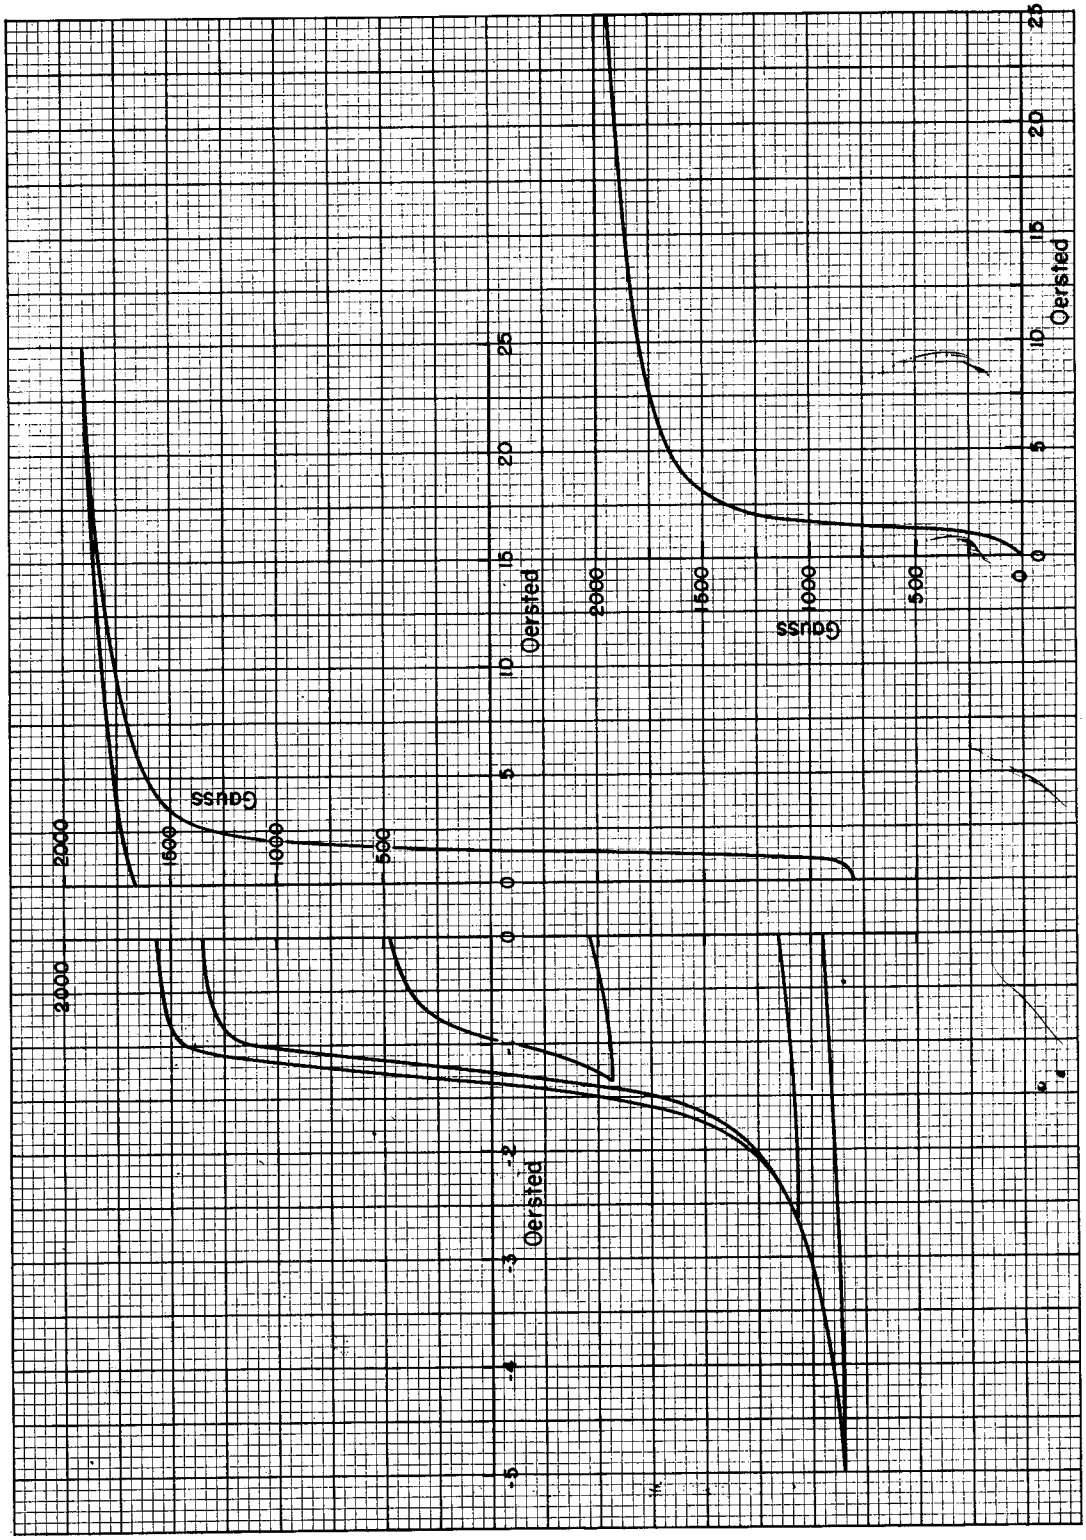

IV B 8. Commercial Ferrite Ceramics

General Ceramics


"Ferramic" 1331 (T = 25°C)

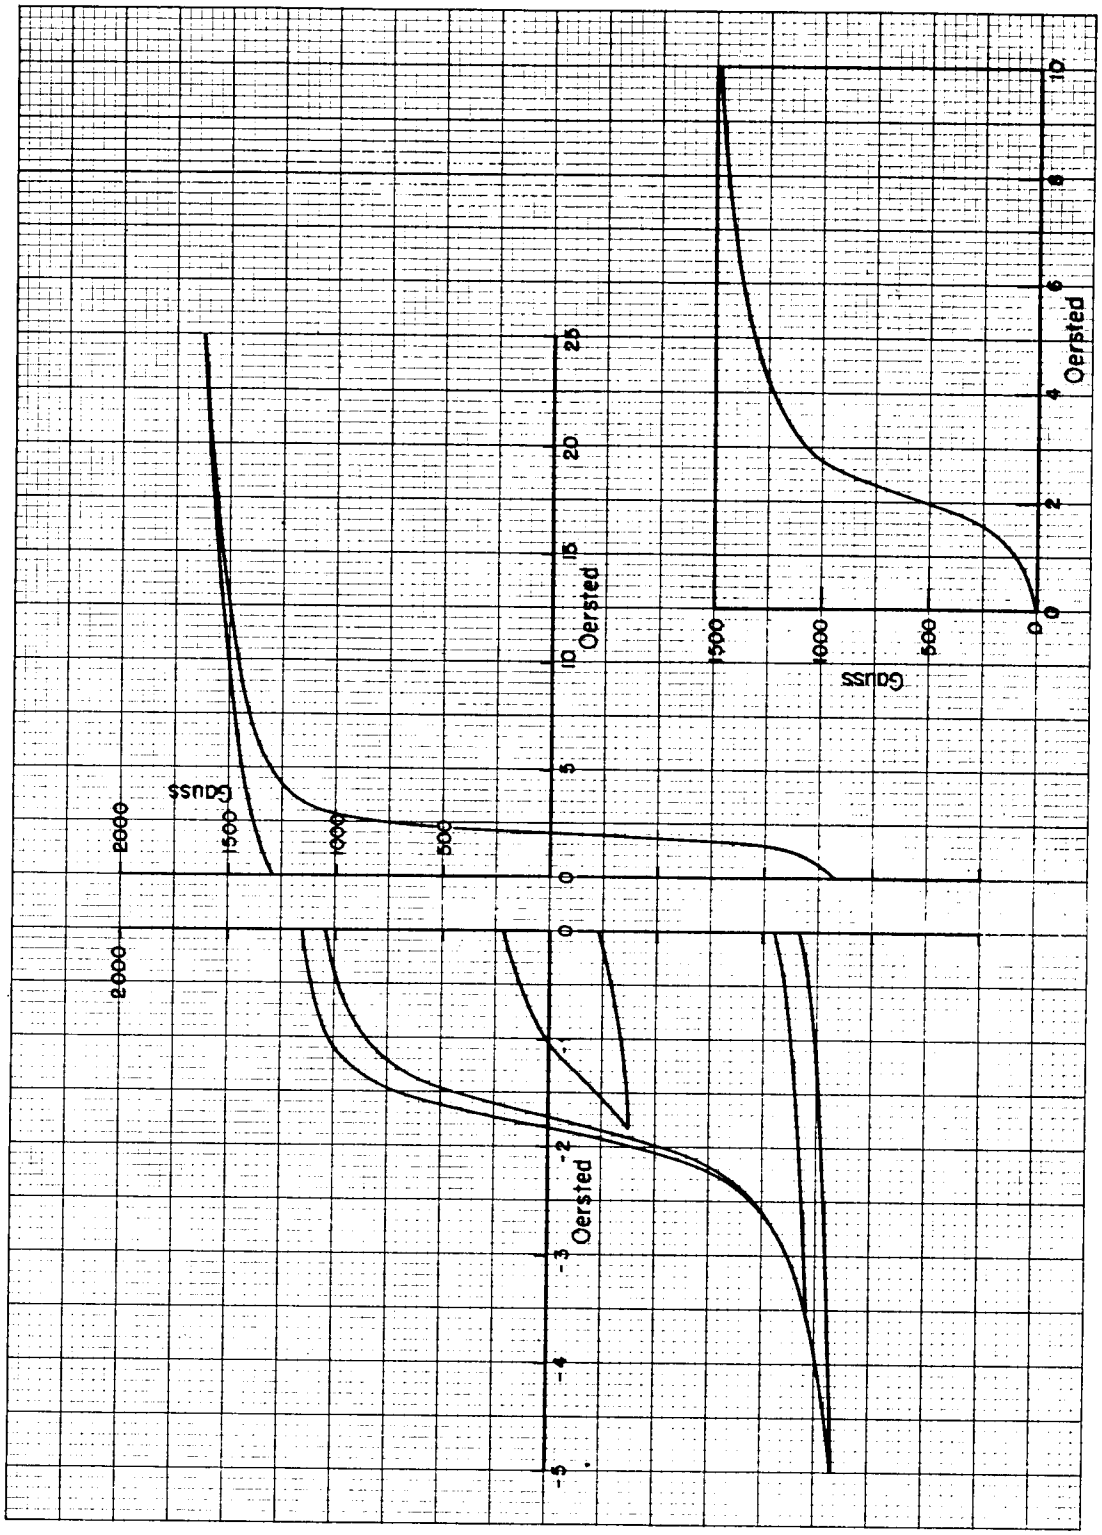

IV B 9. Magnetic-Plastic Mixture


"Ferrotron" Core Material, Type 119

Polymer Corp.

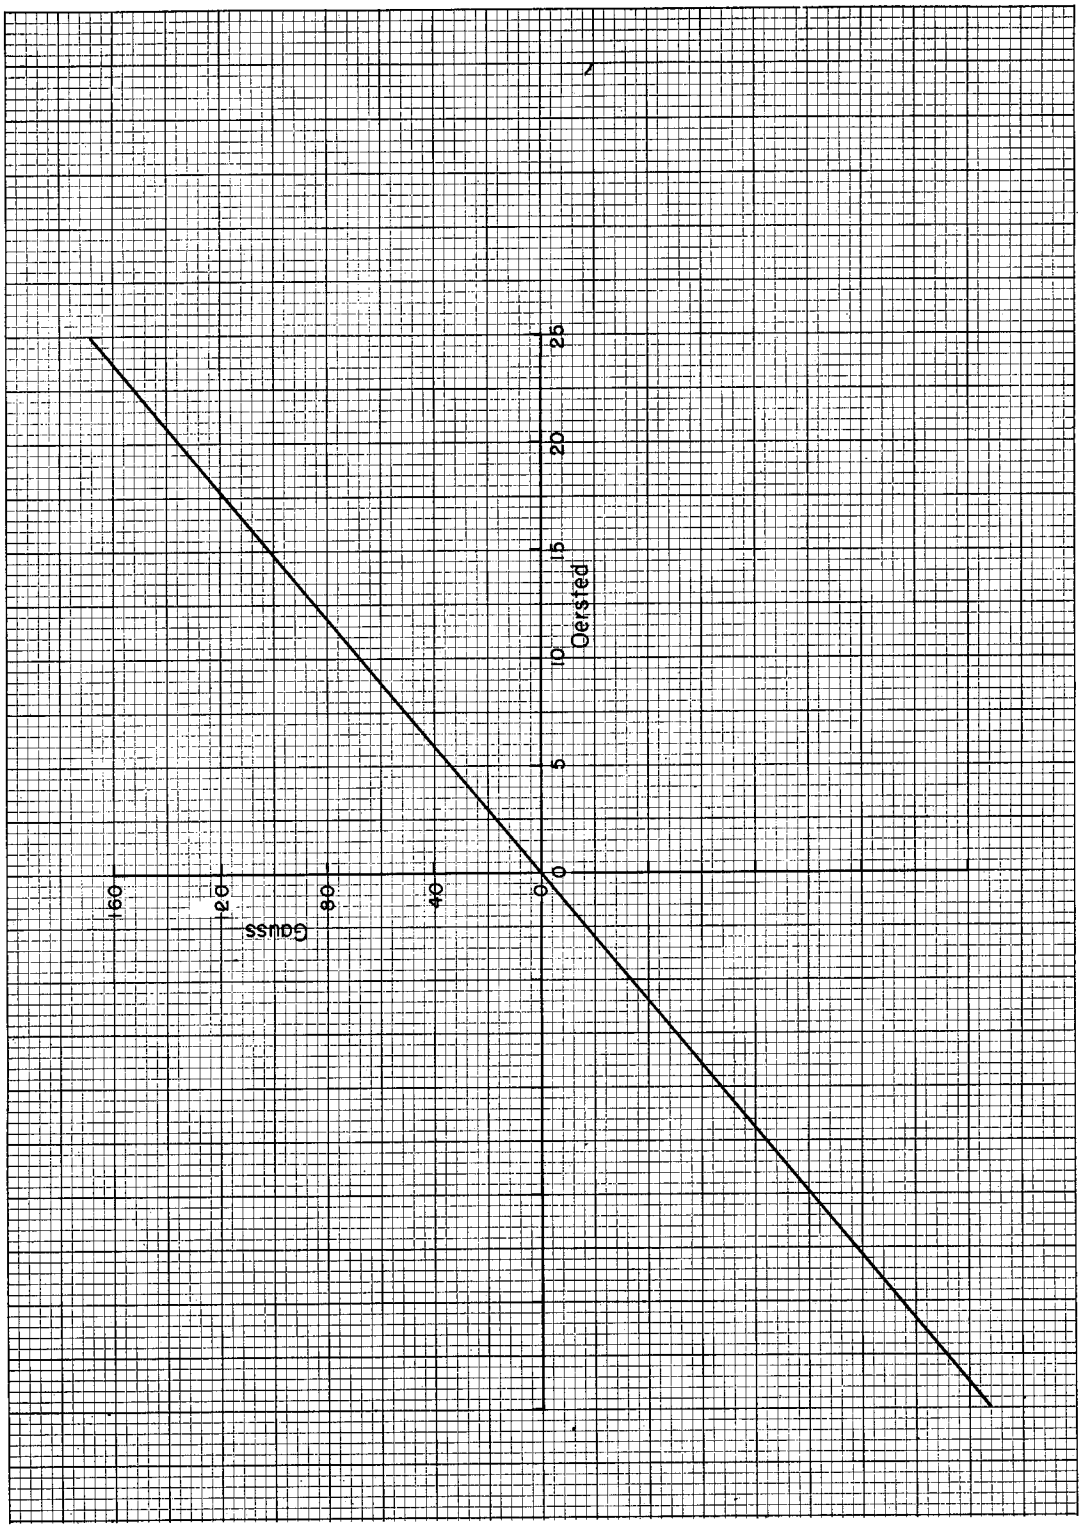


V. Attenuator Characteristics (Attenuation, Phase Shift, and Intrinsic Impedance)

A. Ferrites

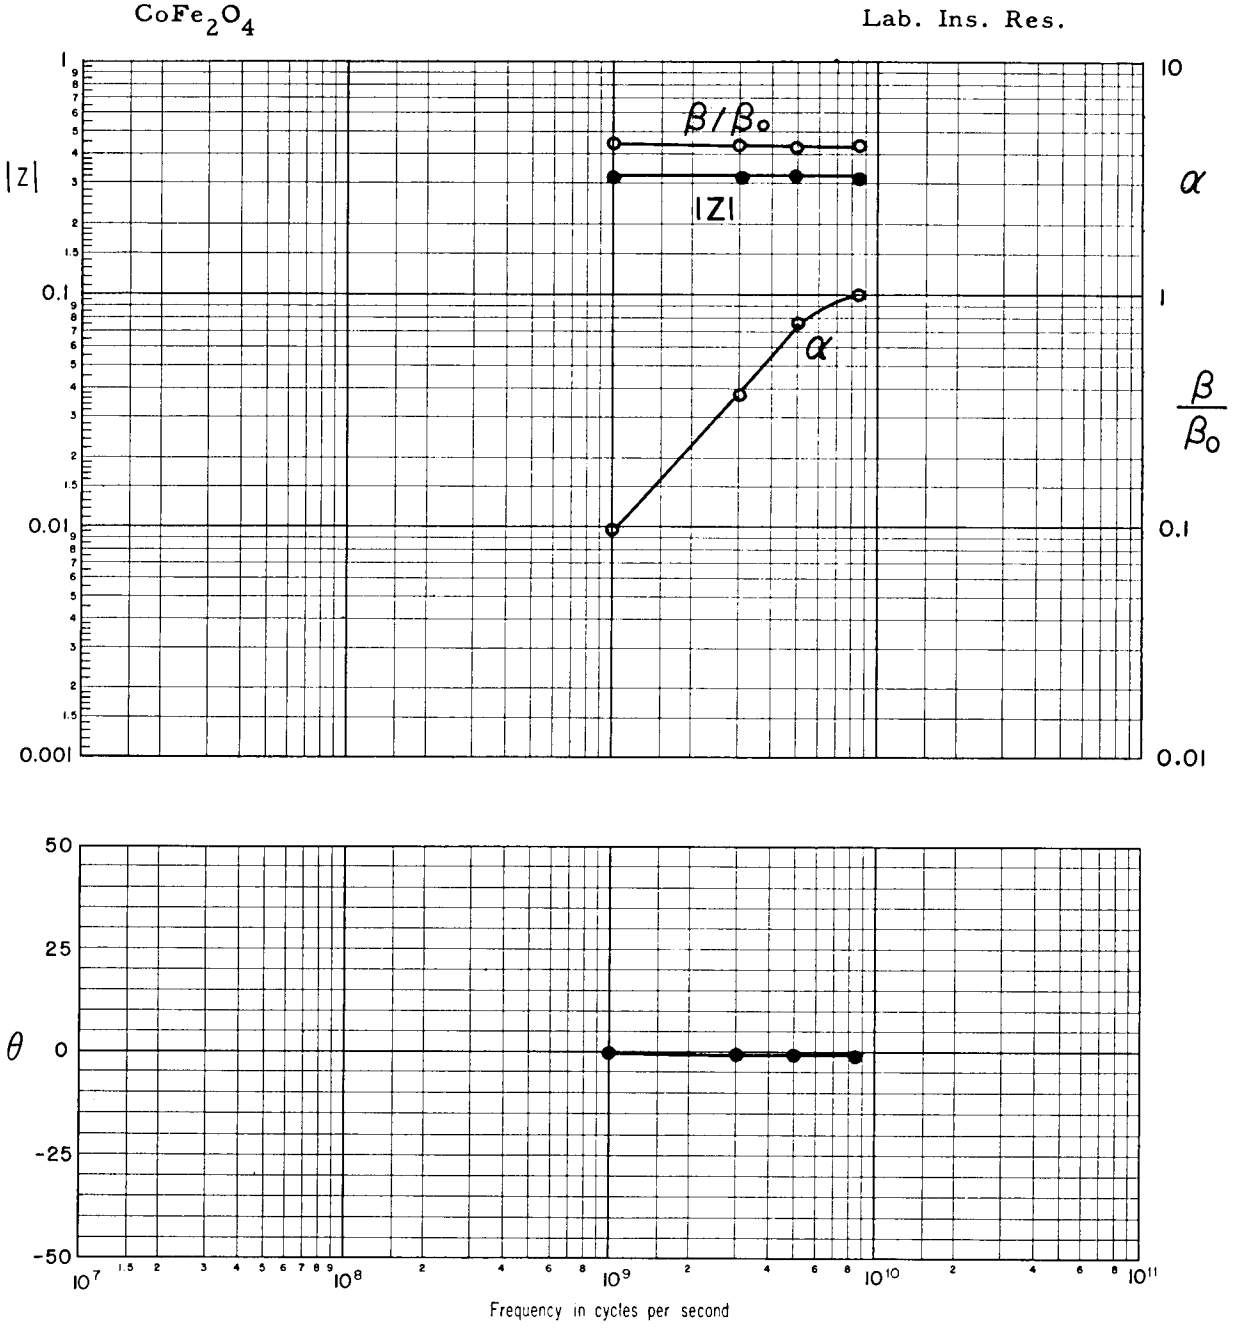



$MgFe_2O_4$ Lab. Ins. Res.

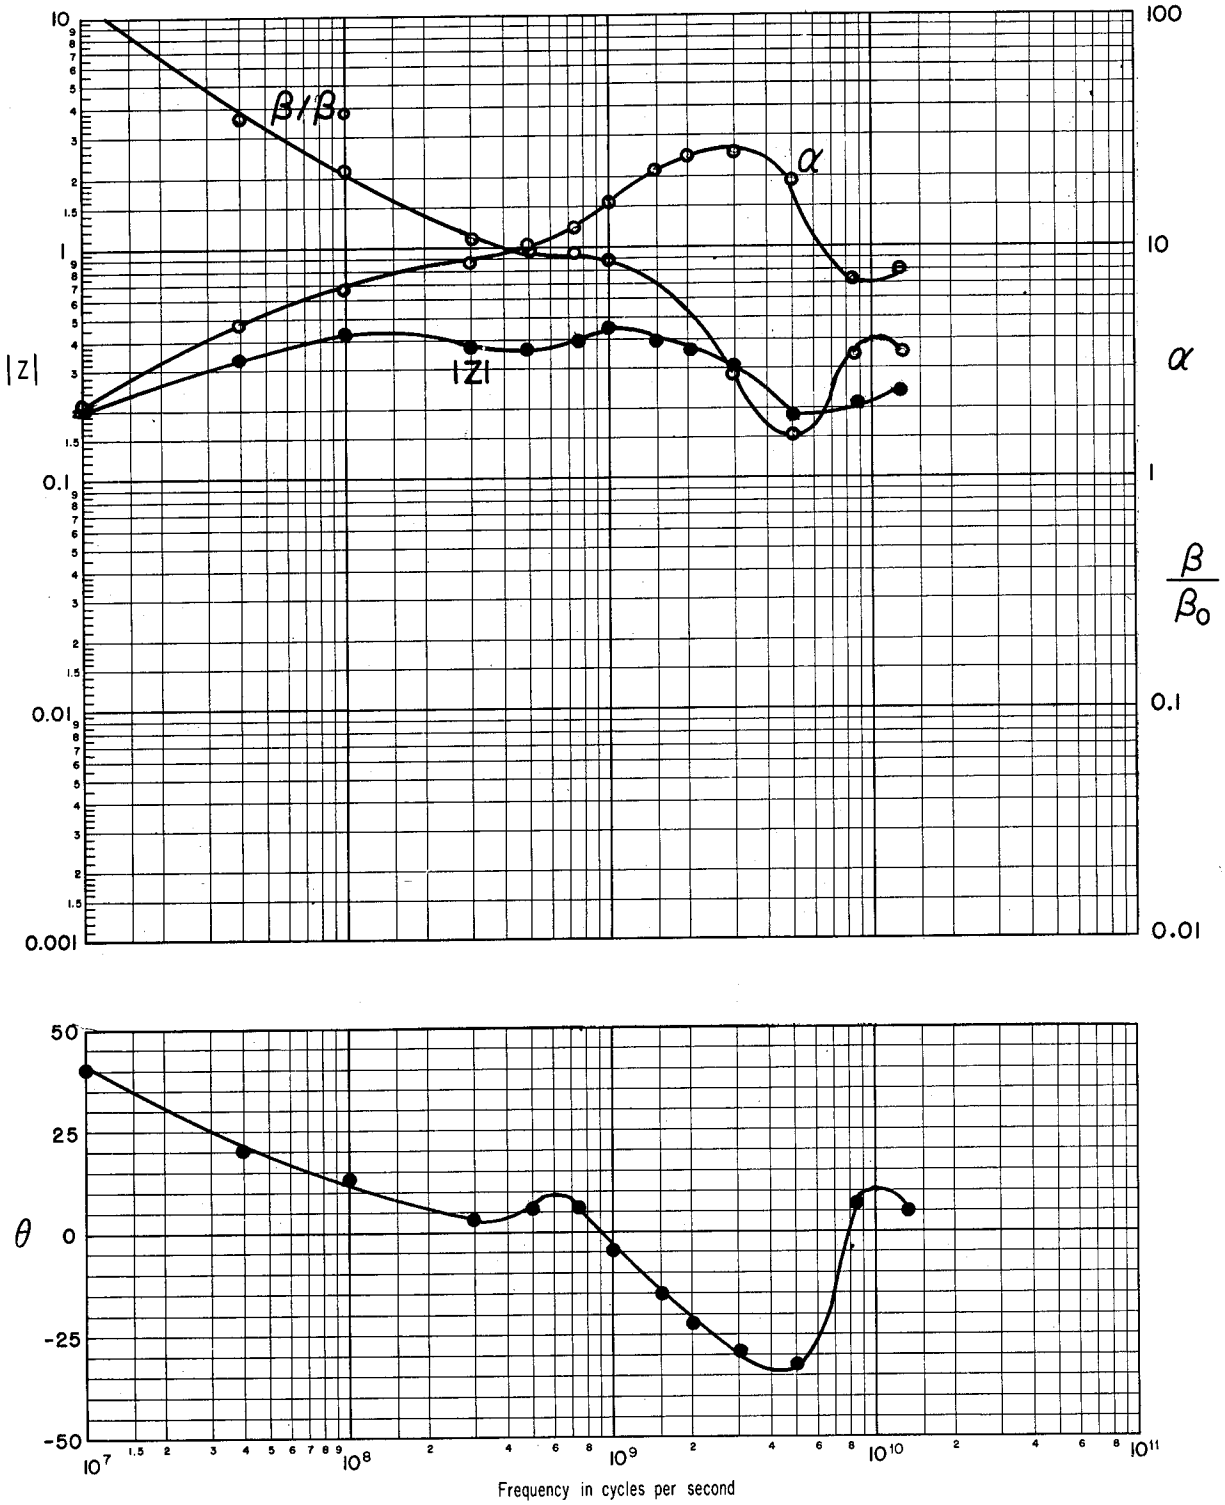


V A. Ferrites

$(MgO)_{0.58}(MnO)_{0.06}(Fe_2O_3)_{0.36}$ Lab. Ins. Res.

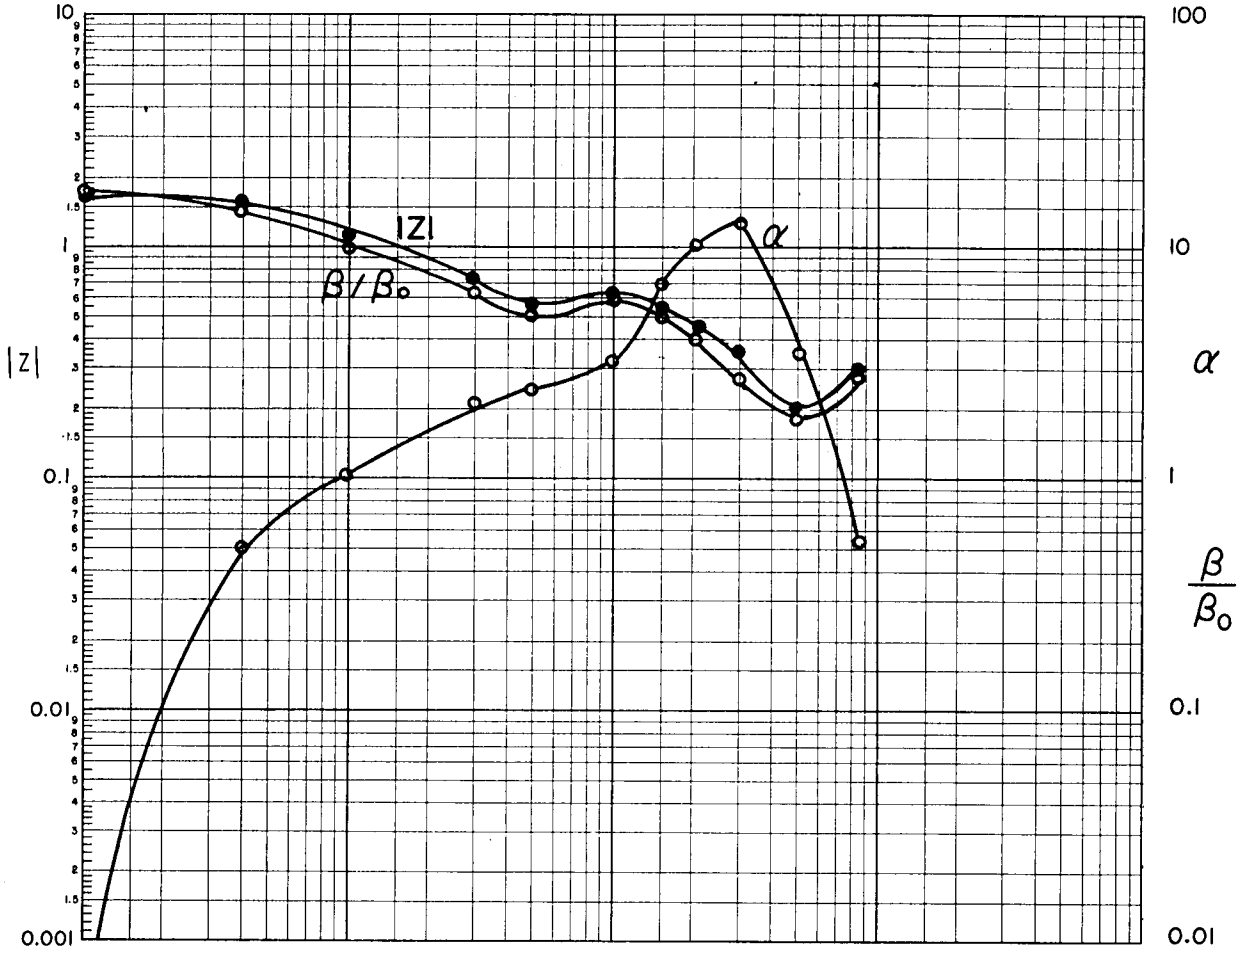


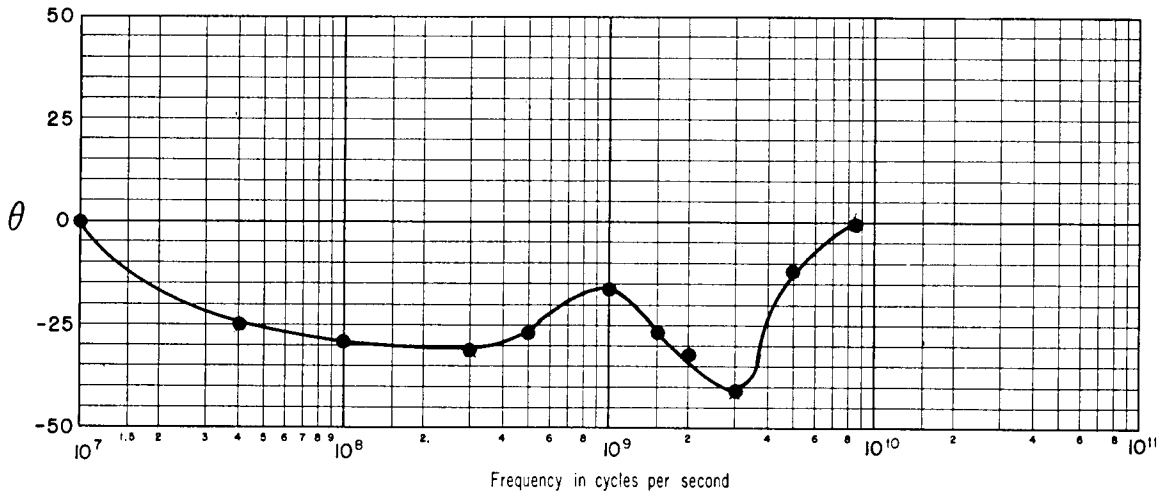


$NiFe_2O_4$ Lab. Ins. Res.

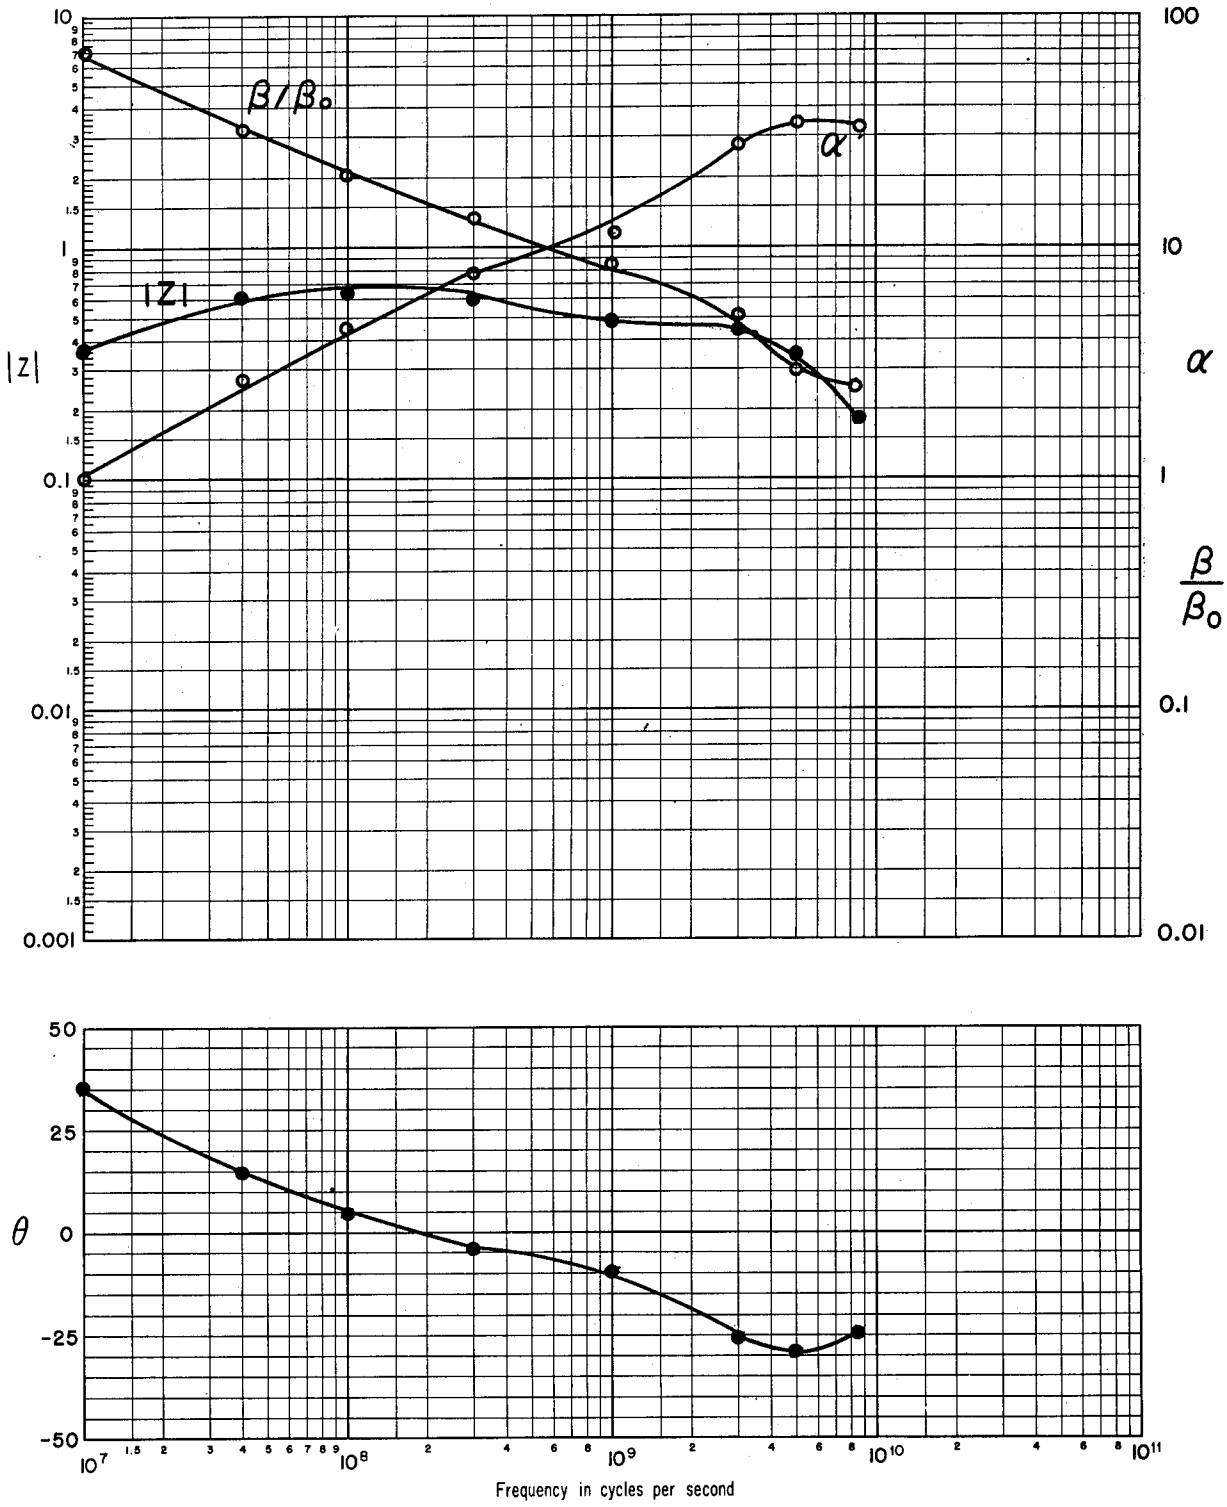


$Ni_{0.9}Zn_{0.1}Fe_2O4$ Lab. Ins. Res.

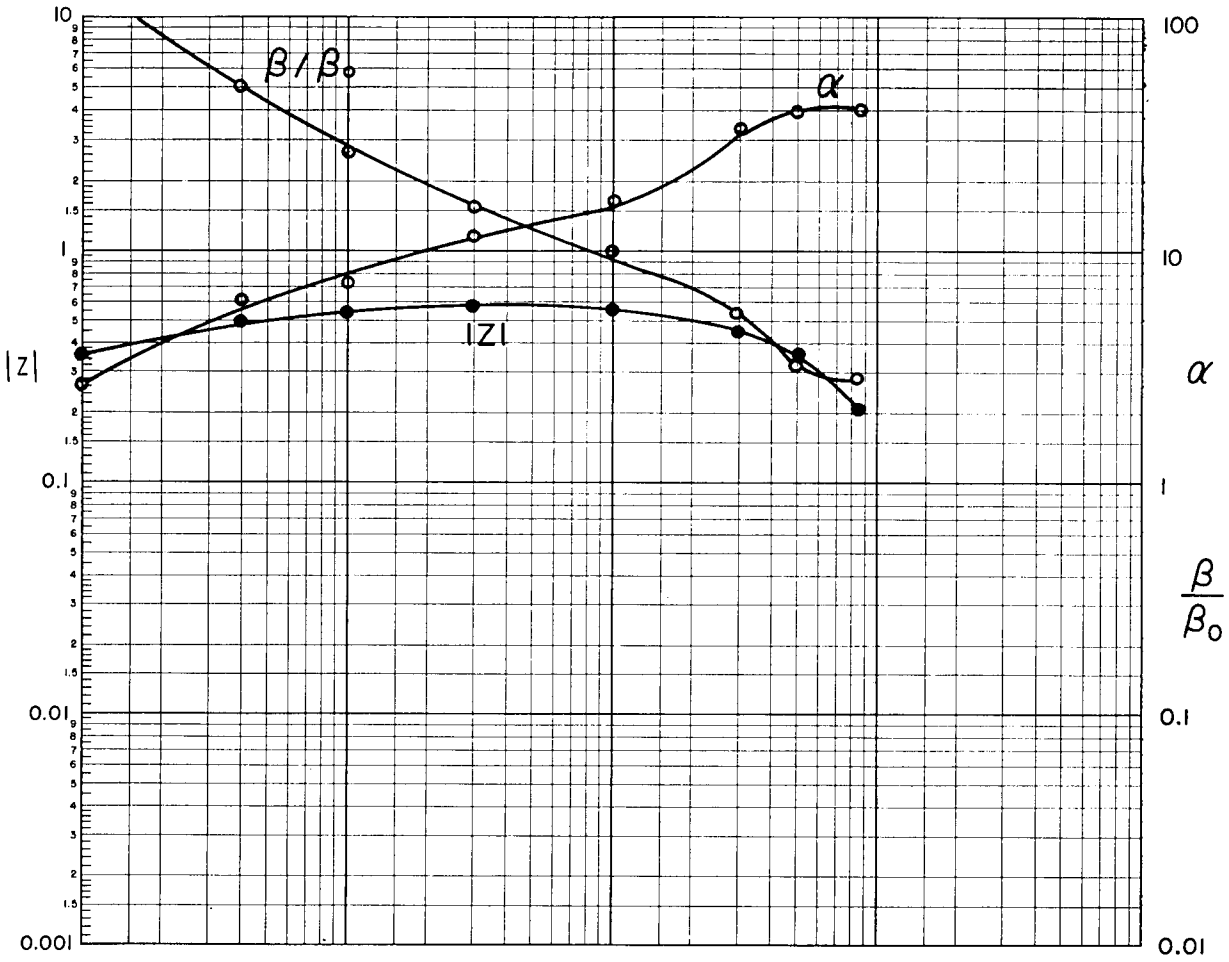

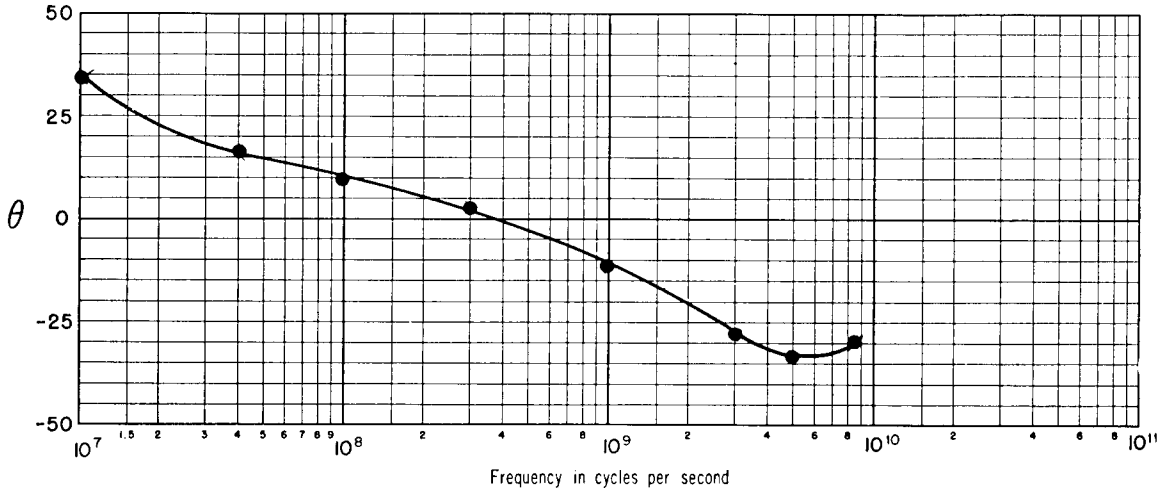


$Ni_{0.8}Zn_{0.2}Fe_2O_4$


Lab. Ins. Res.

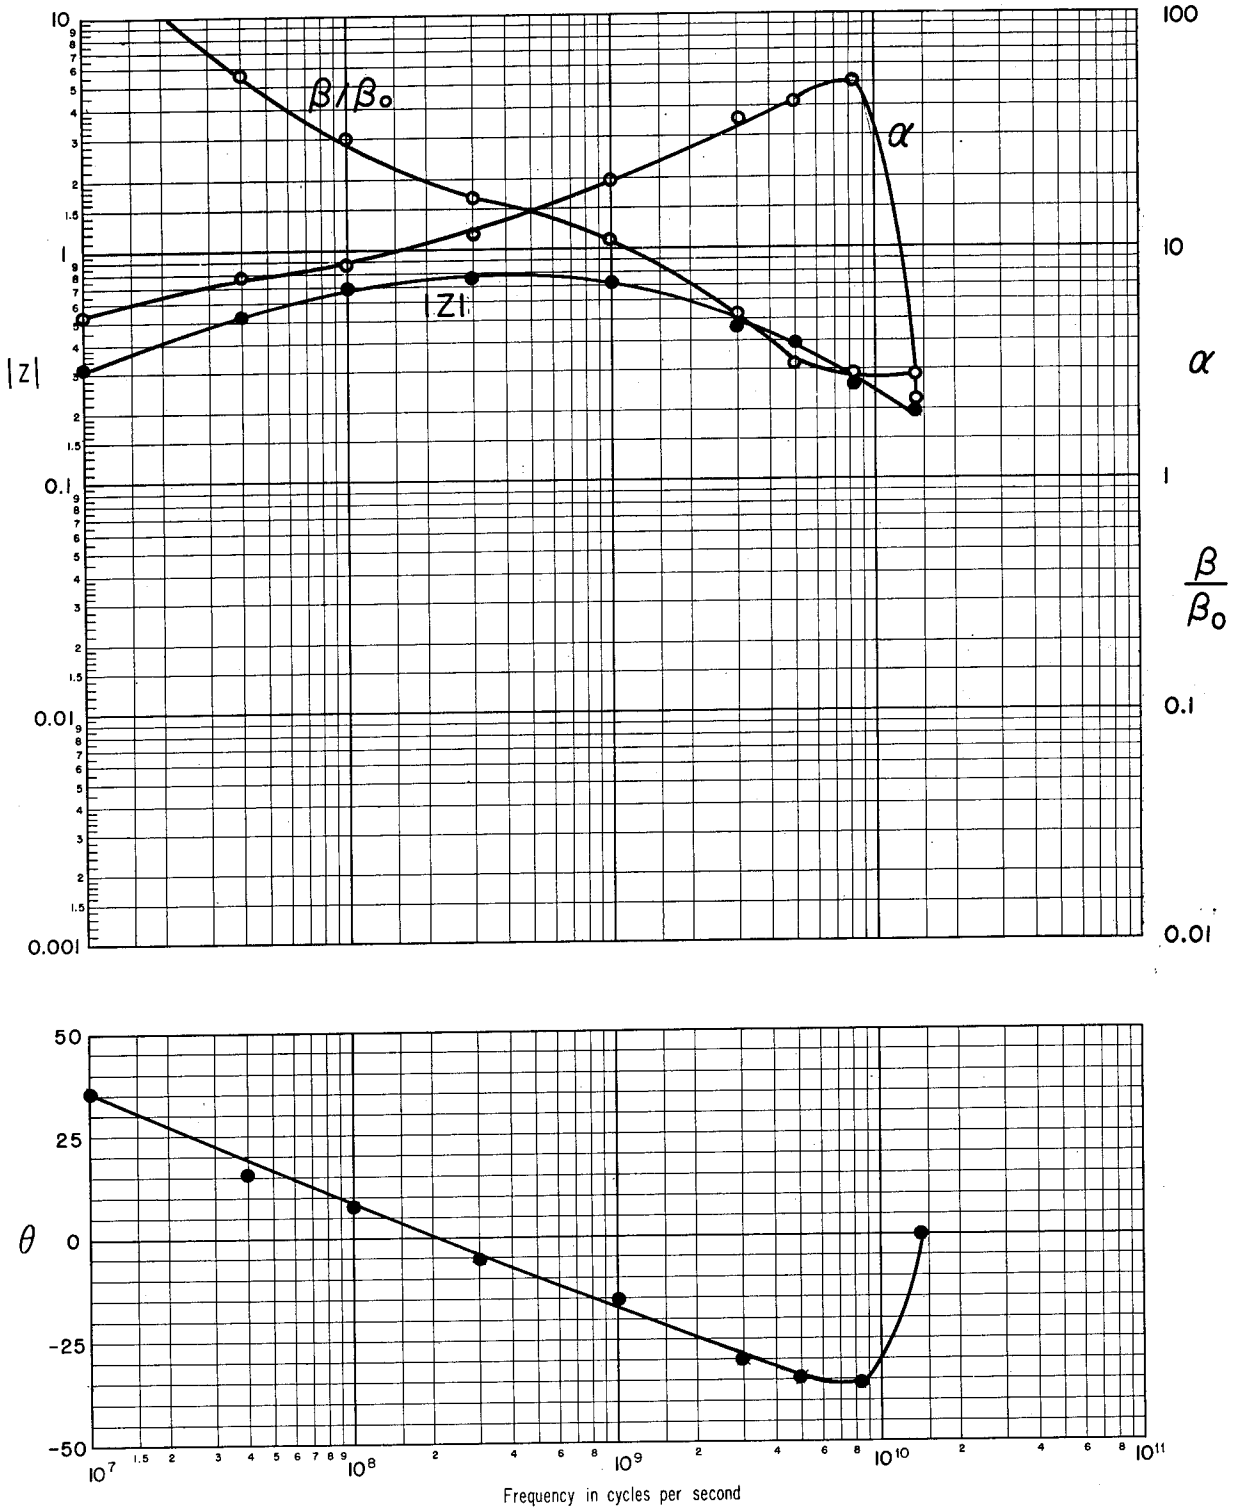


$Ni_{0.7}Zn_{0.3}Fe_2O_4$ Lab. Ins. Res.

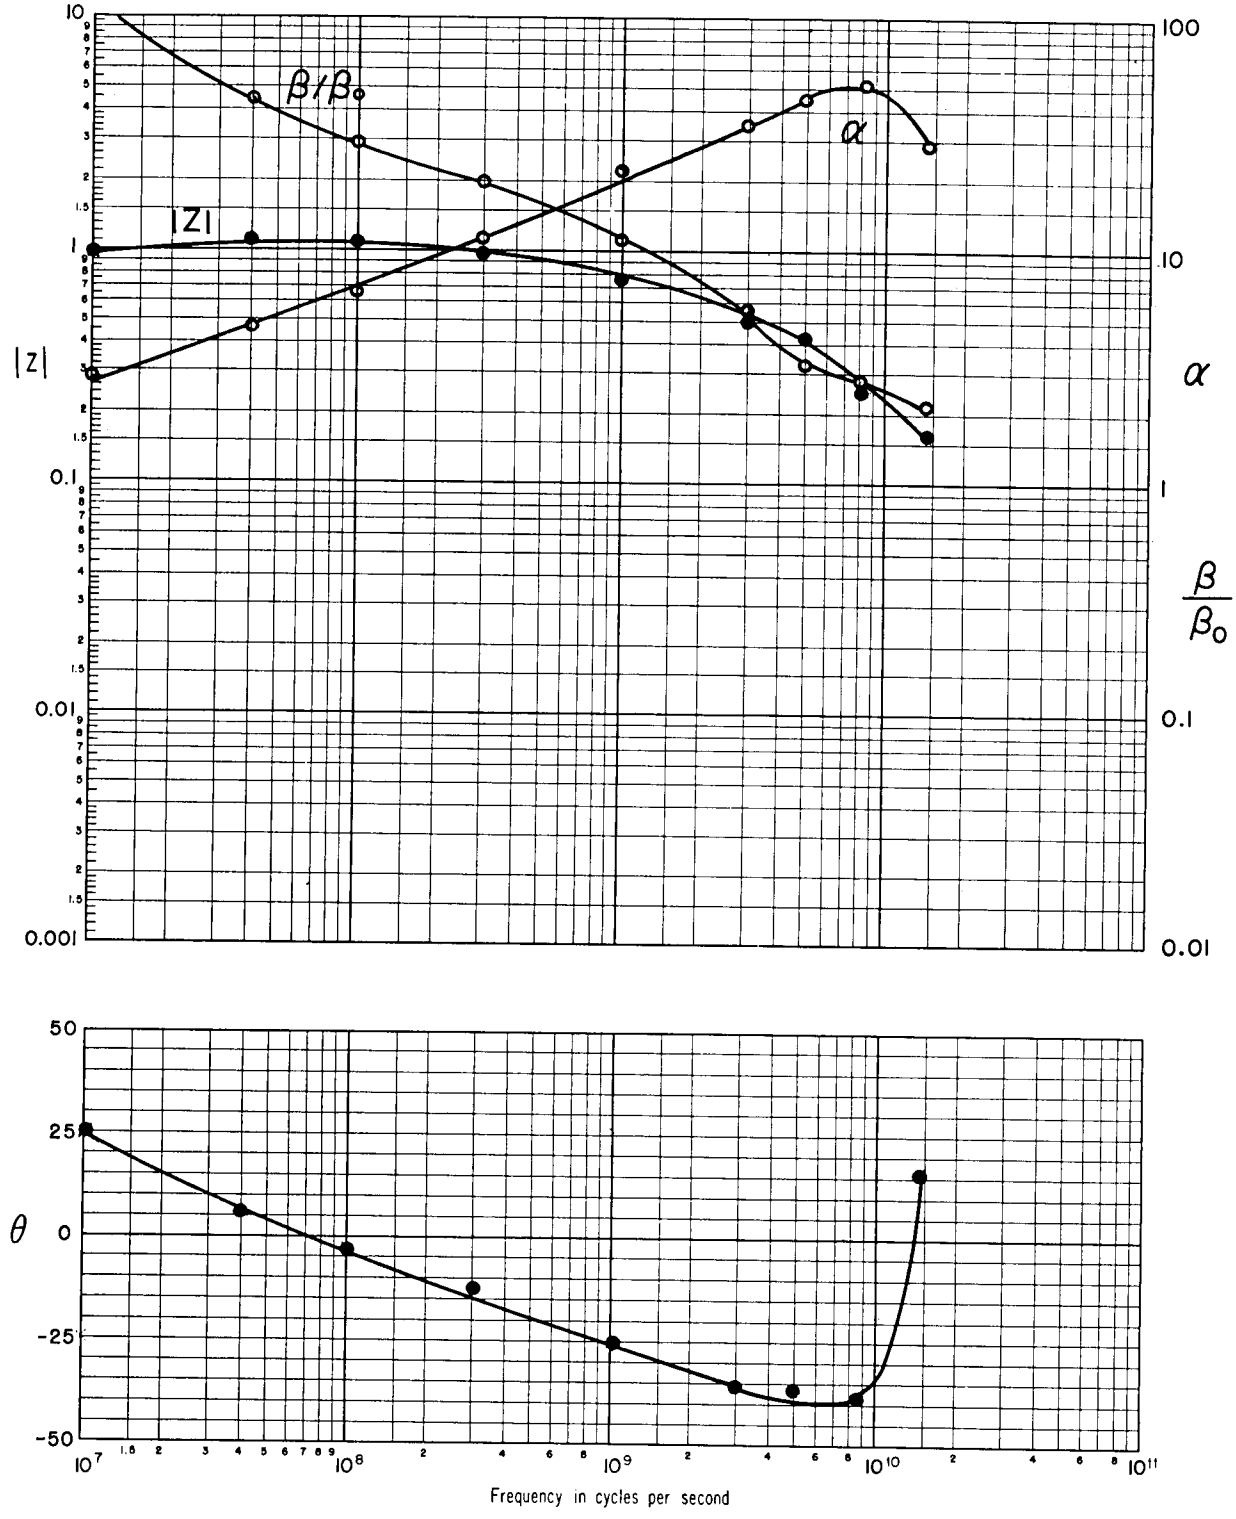

$Ni_{0.6}Zn_{0.4}Fe_2O_4$ Lab. Ins. Res.

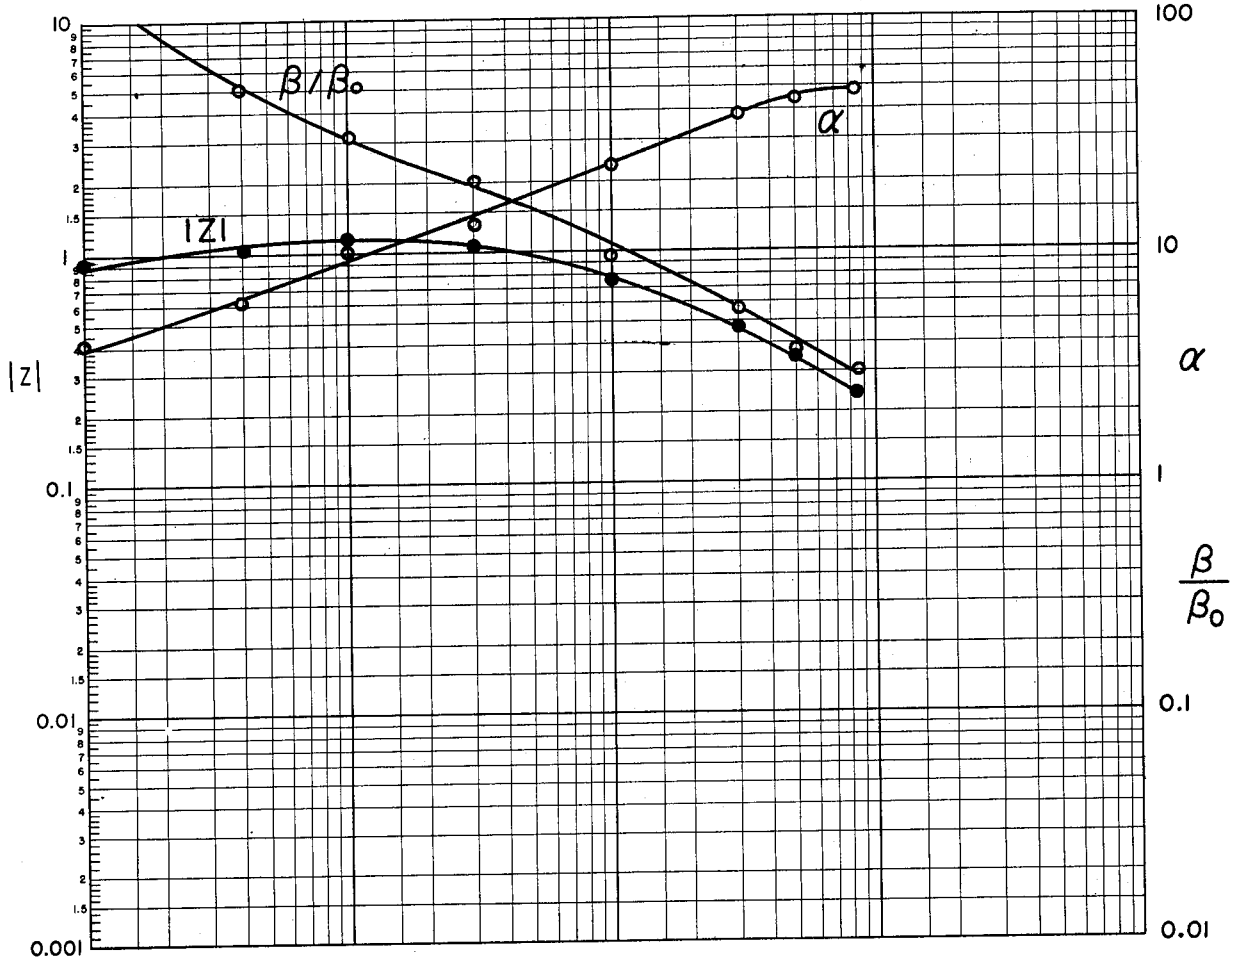


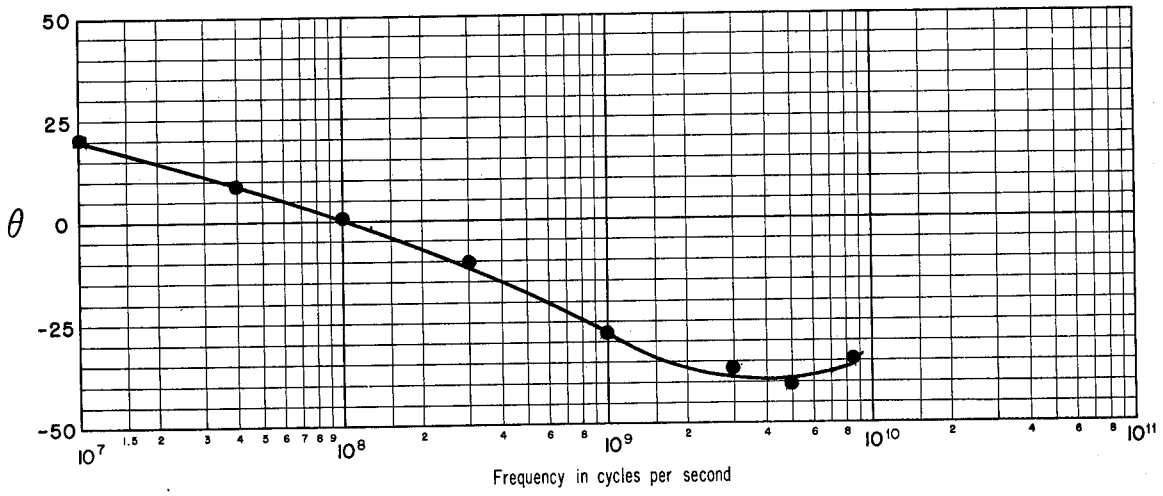


V A. Ferrites

$Ni_{0.5}Zn_{0.5}Fe_2O_4$


Lab. Ins. Res.

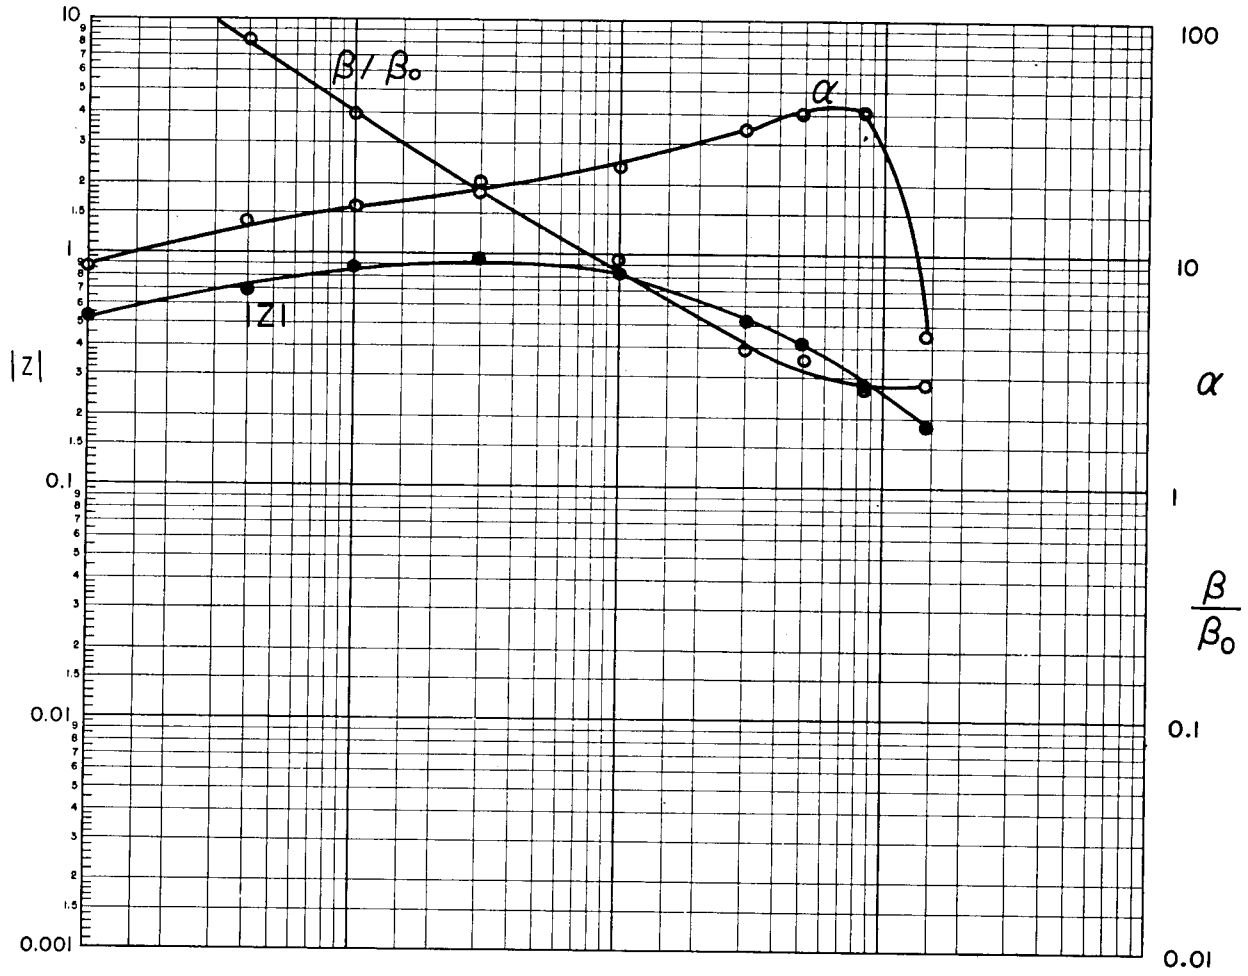

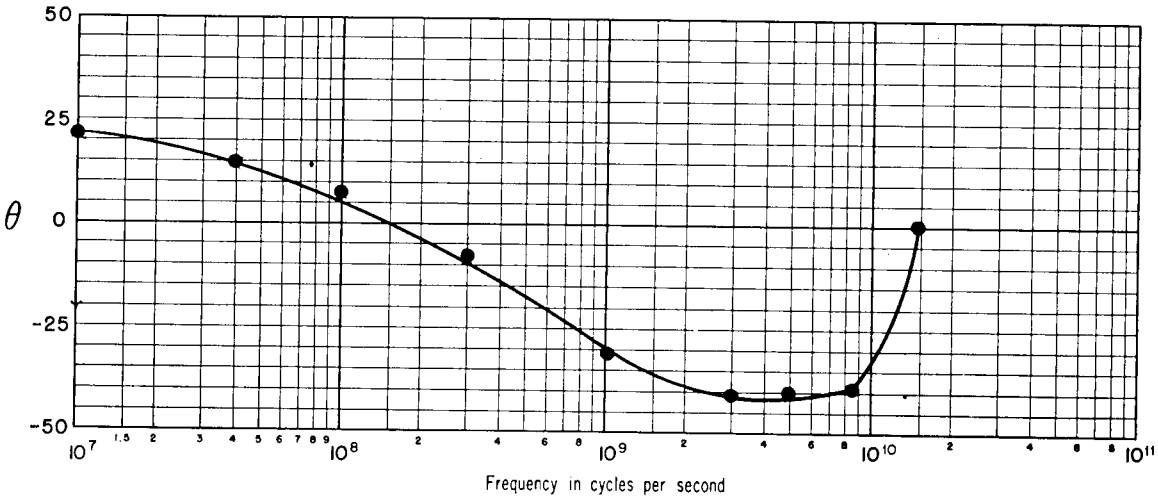


$Ni_{0.4}Zn_{0.6}Fe_2O_4$

Lab. Ins. Res.

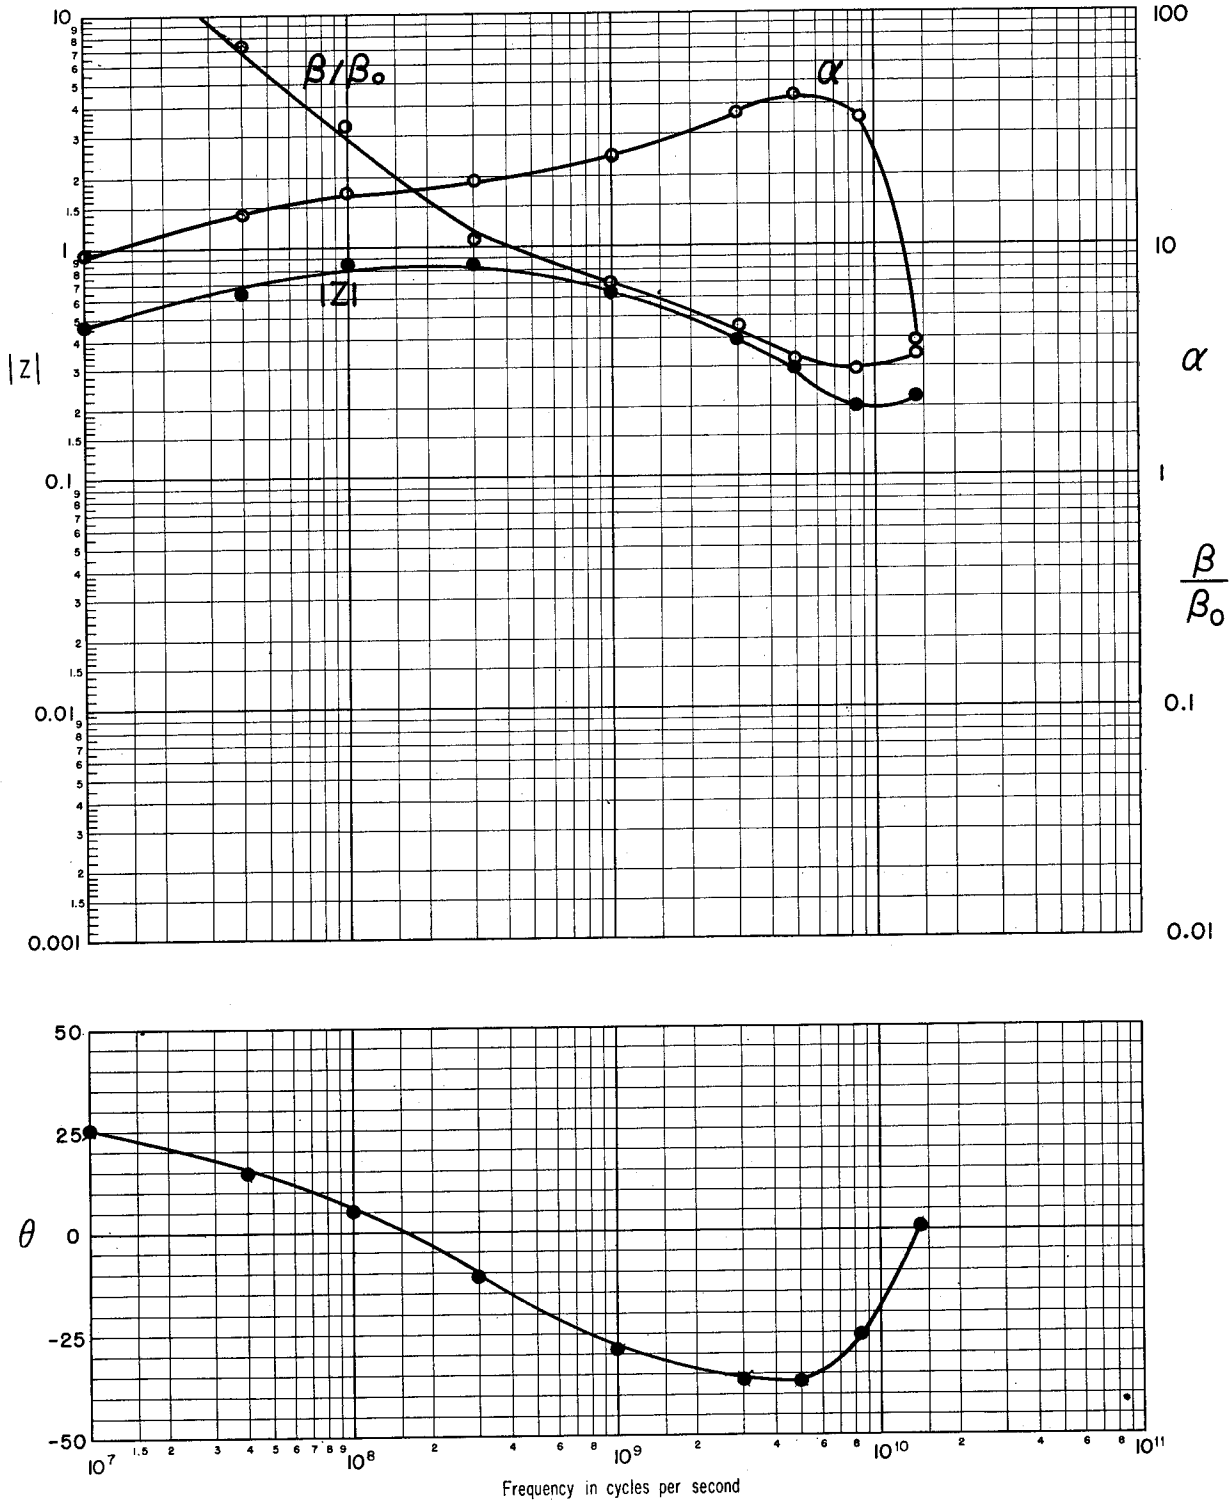



$Ni_{0.3}Zn_{0.7}Fe_2O_4$

Lab. Ins. Res.

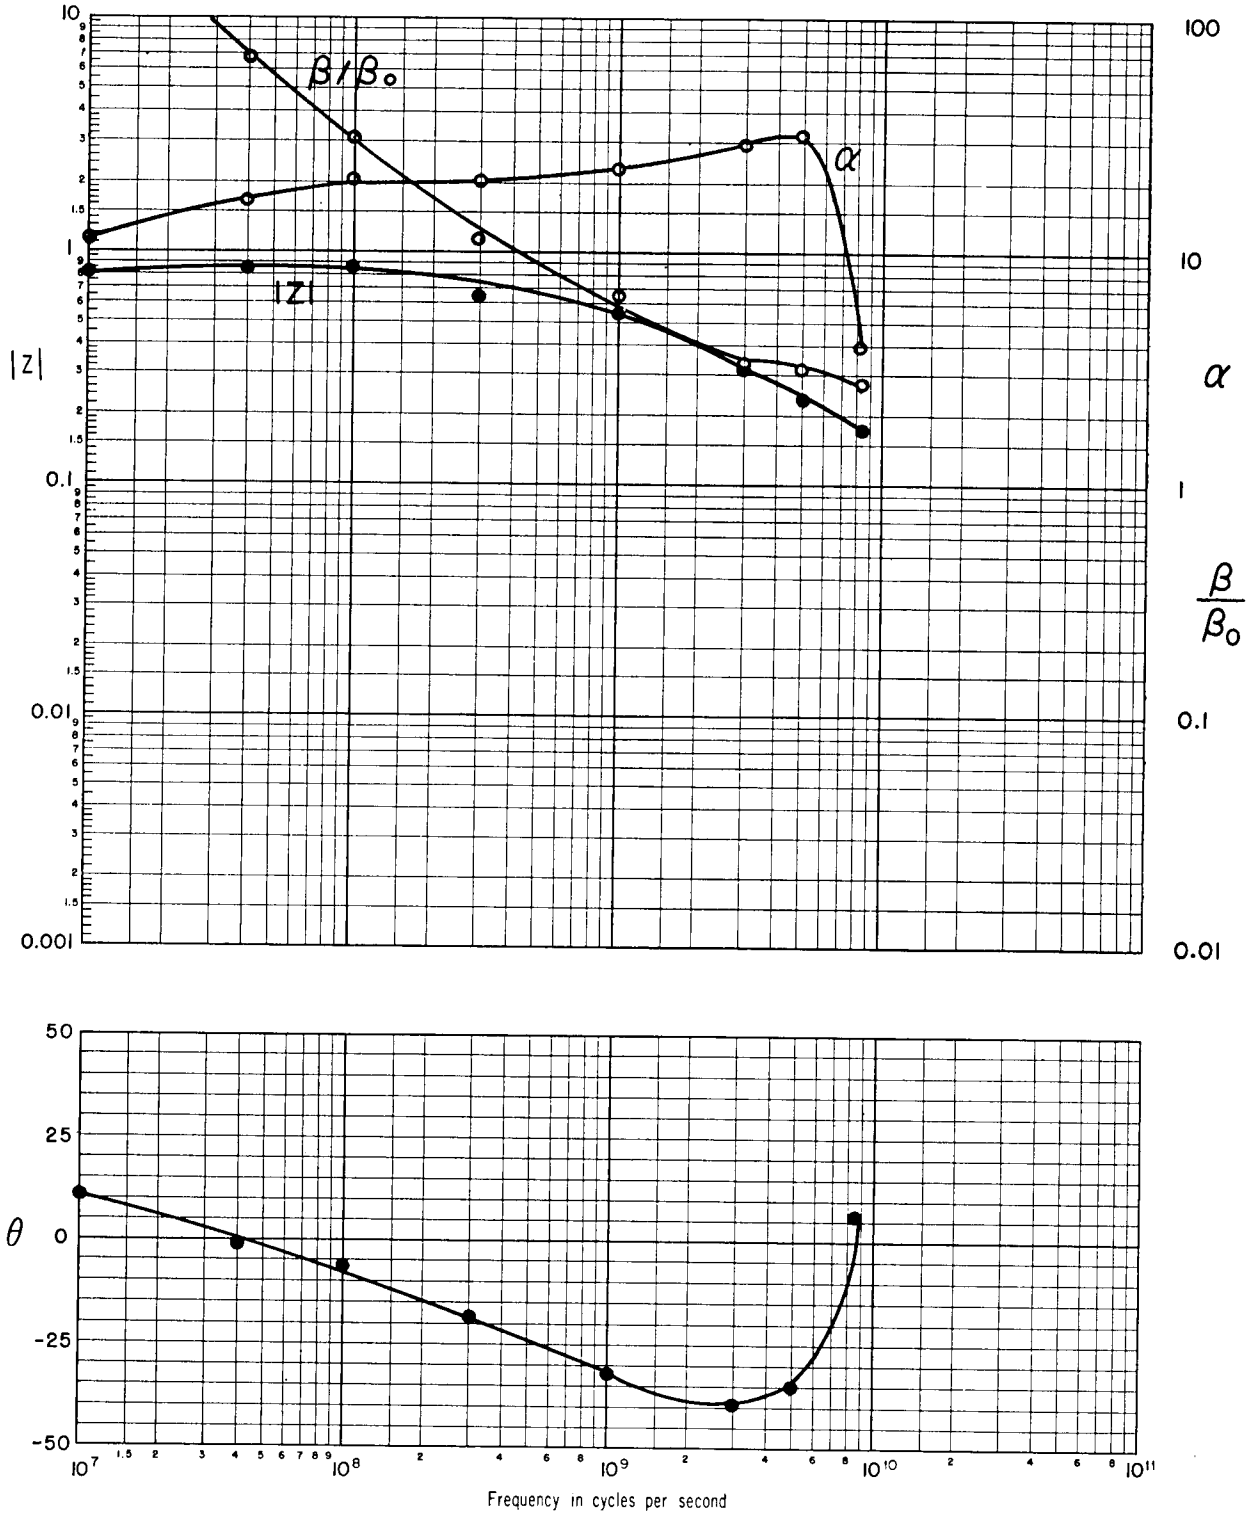


"Crowloy"20 Crowley

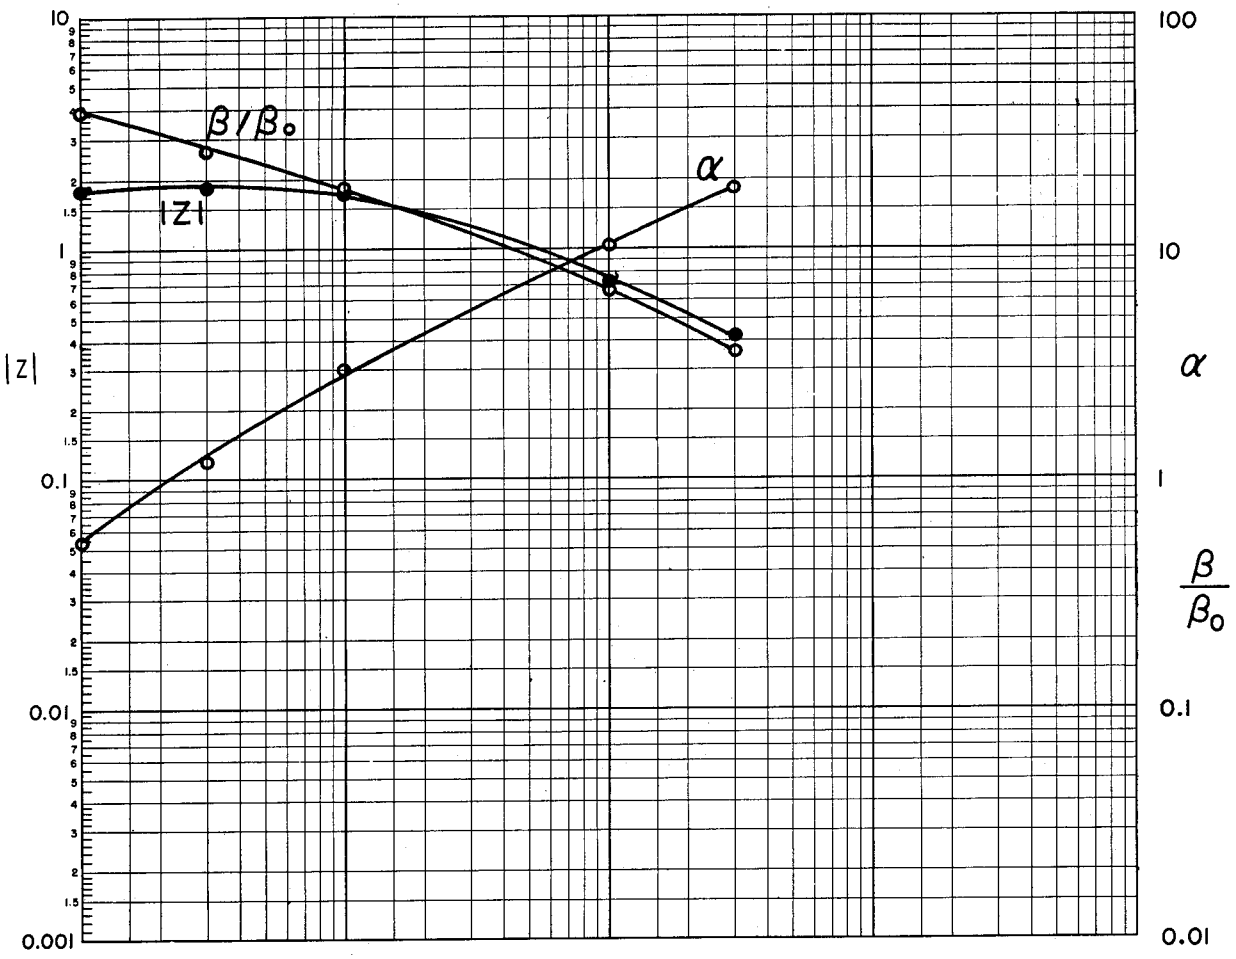

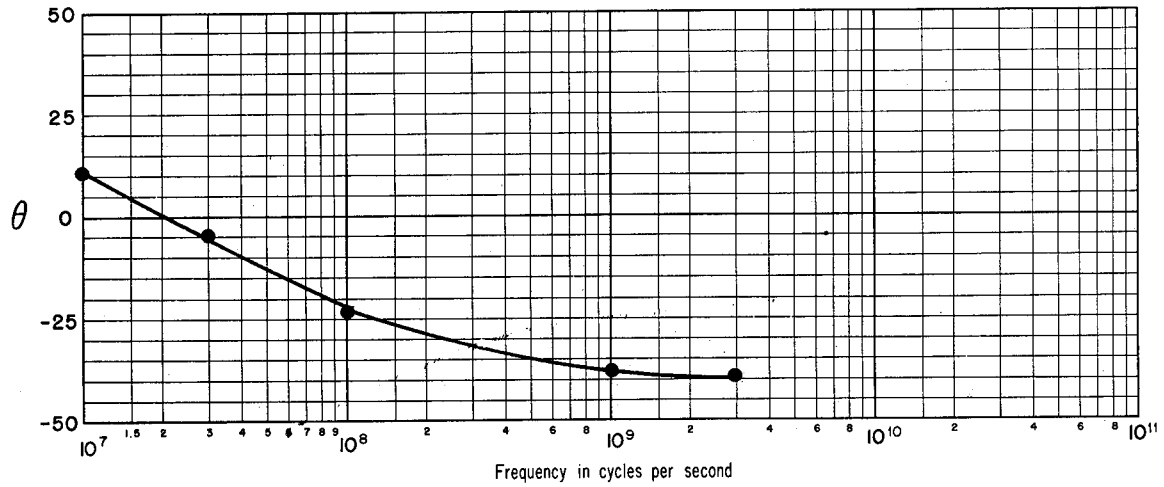


V A. Ferrites

"Crowloy" BX113 Crowley

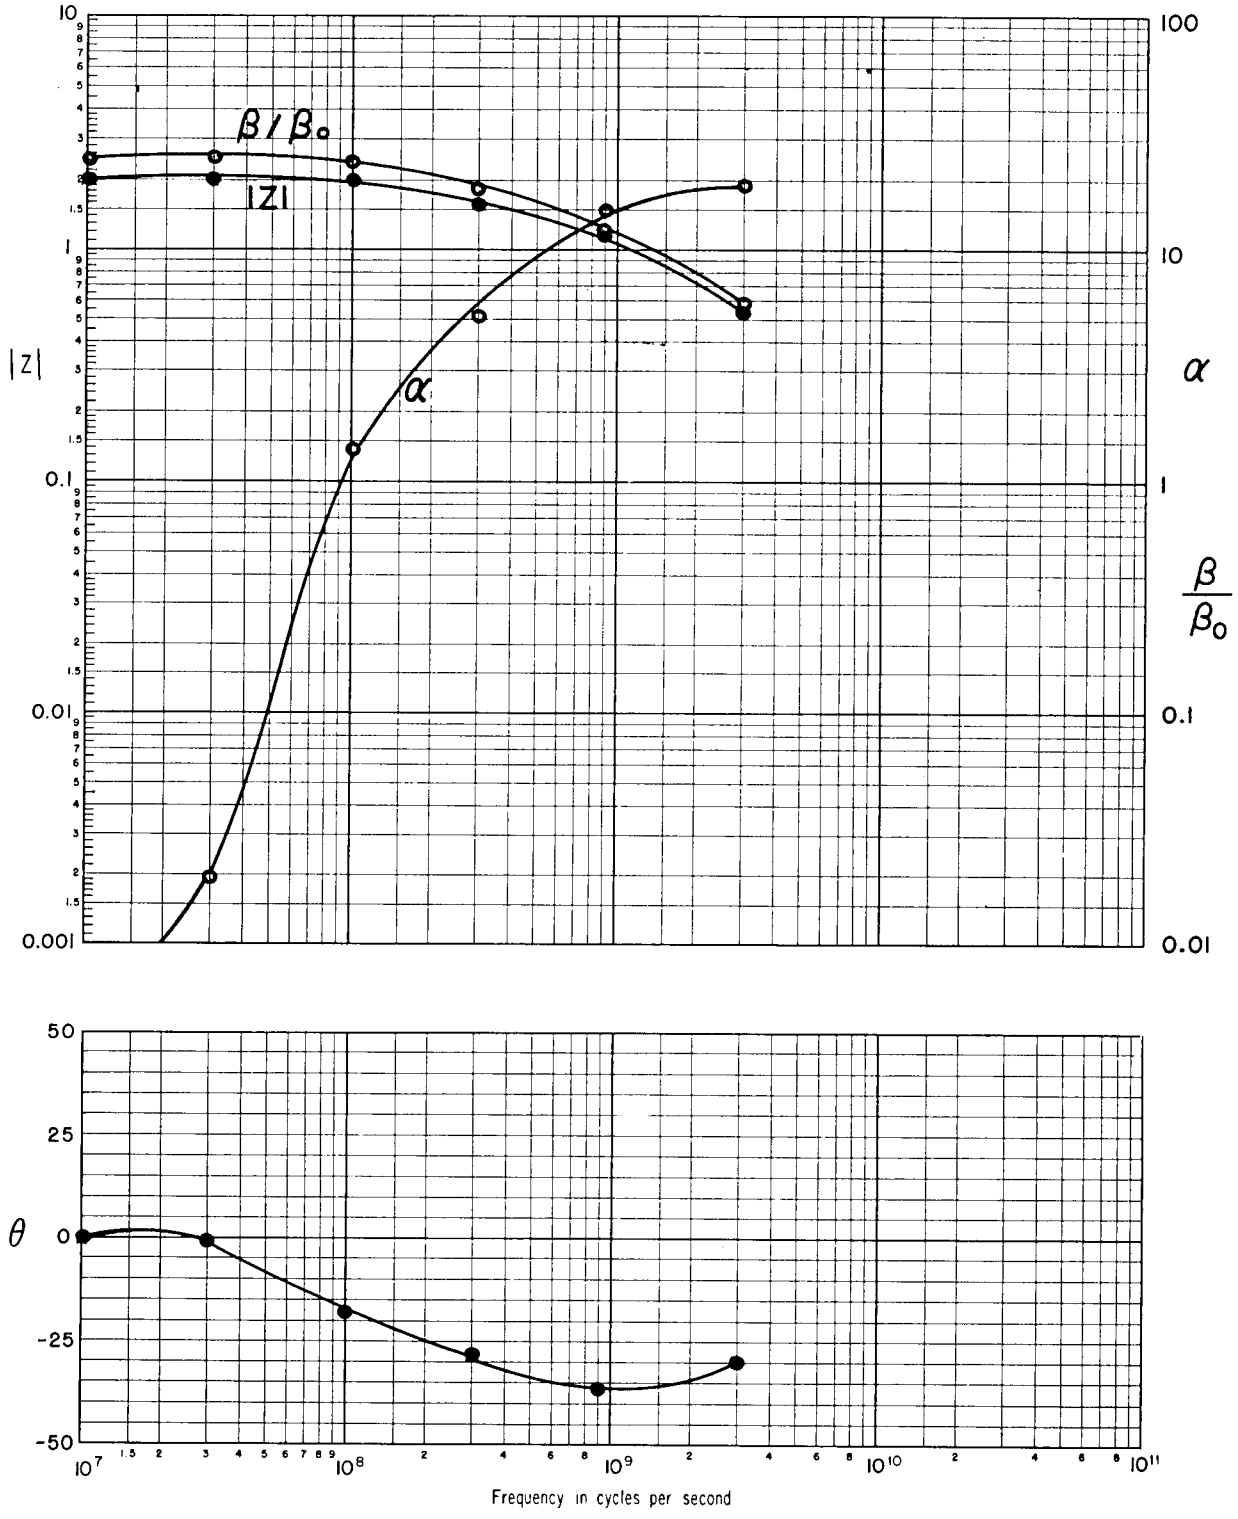

V A. Ferrites


"Crowloy" BX114 — Crowley

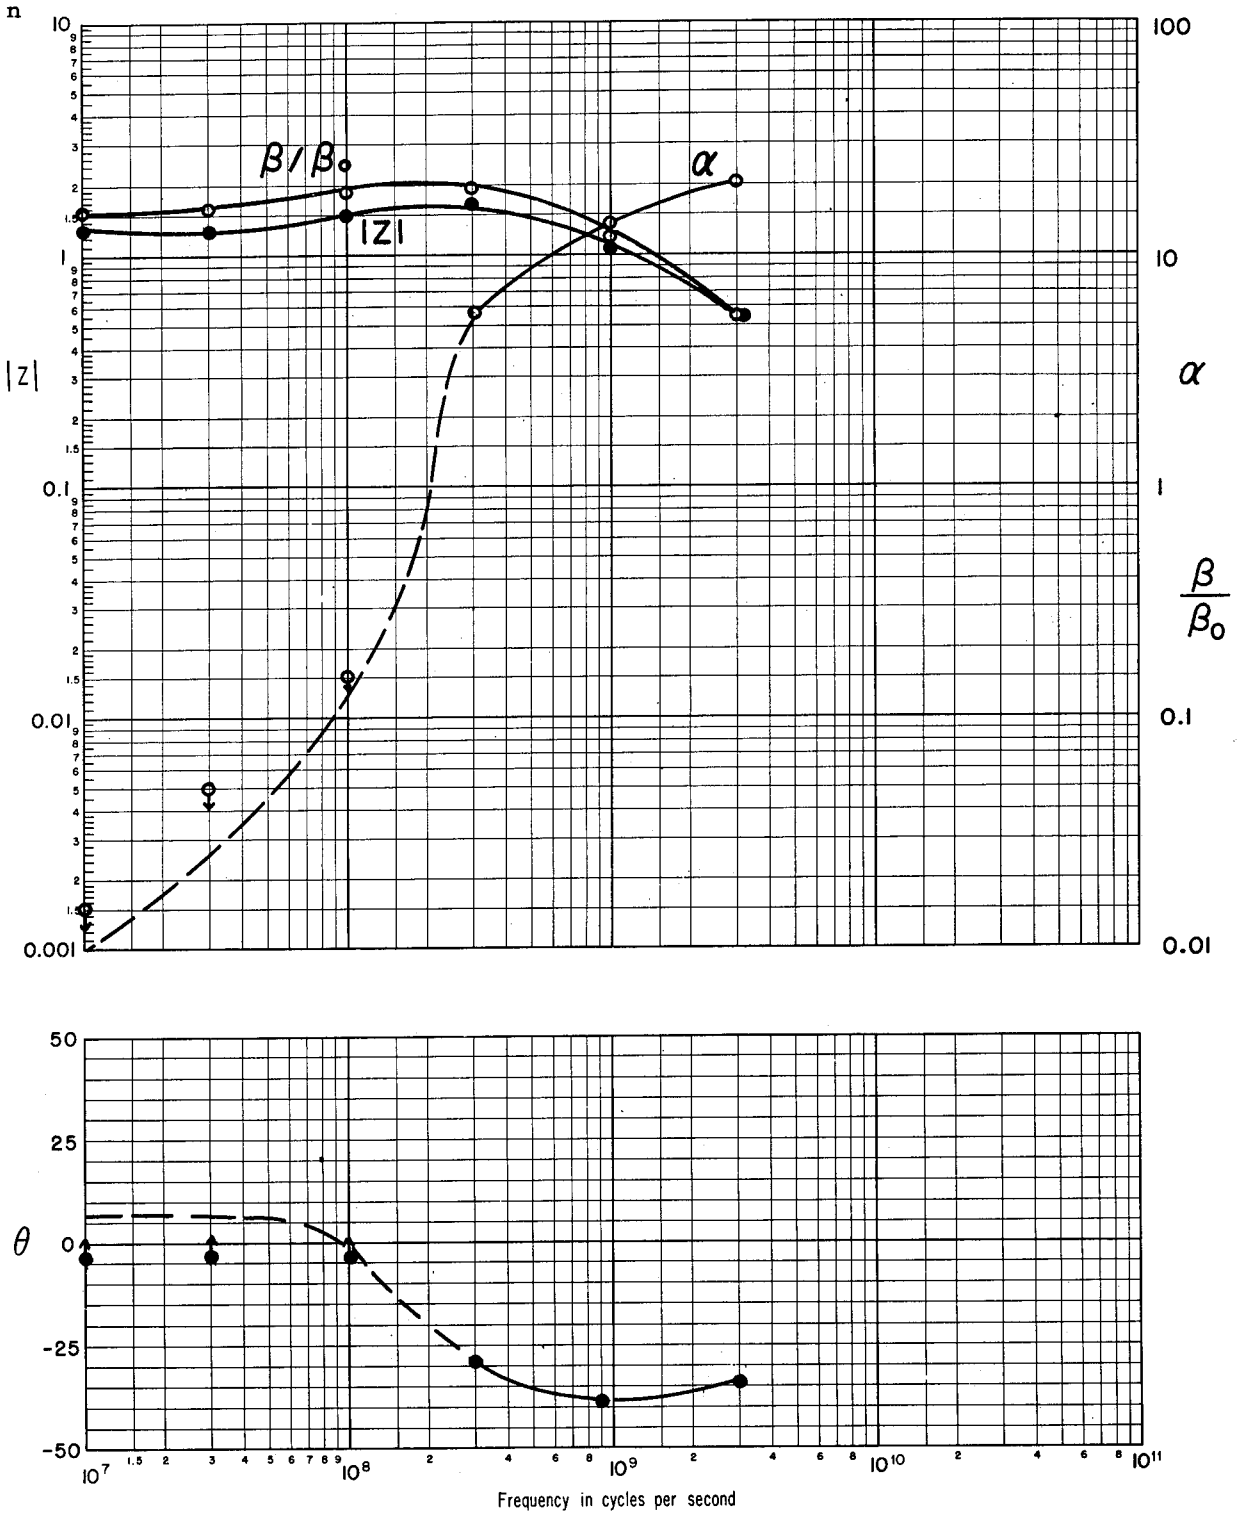


V A. Ferrites

"Ferramic" A

General Ceramics

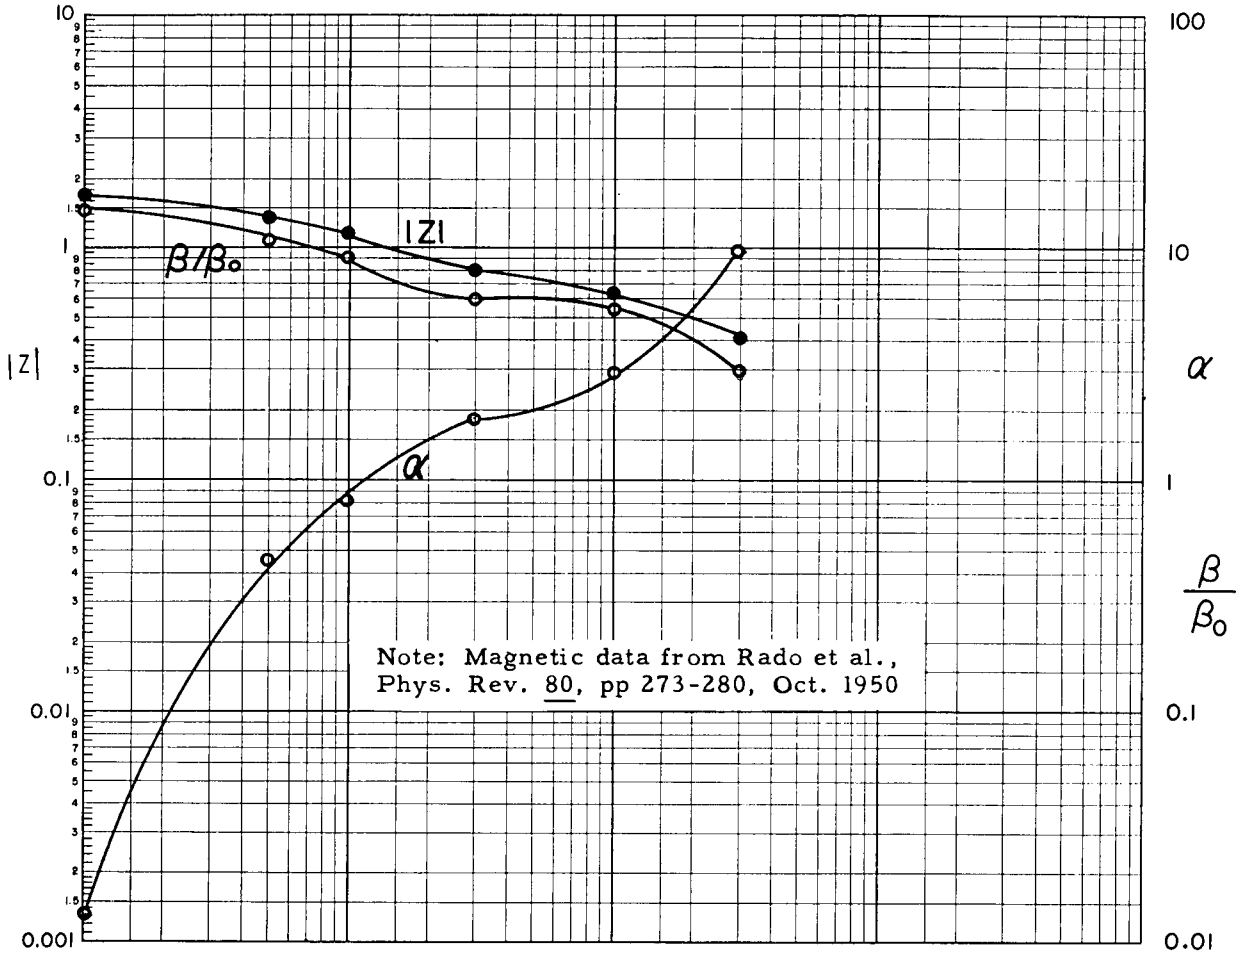


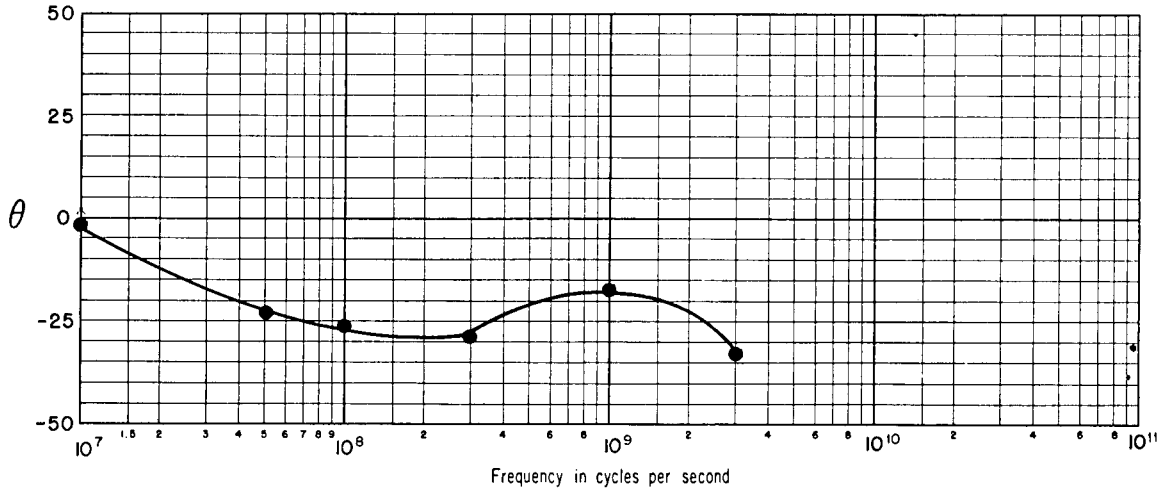

"Ferramic" B


V A. Ferrites

General Ceramics

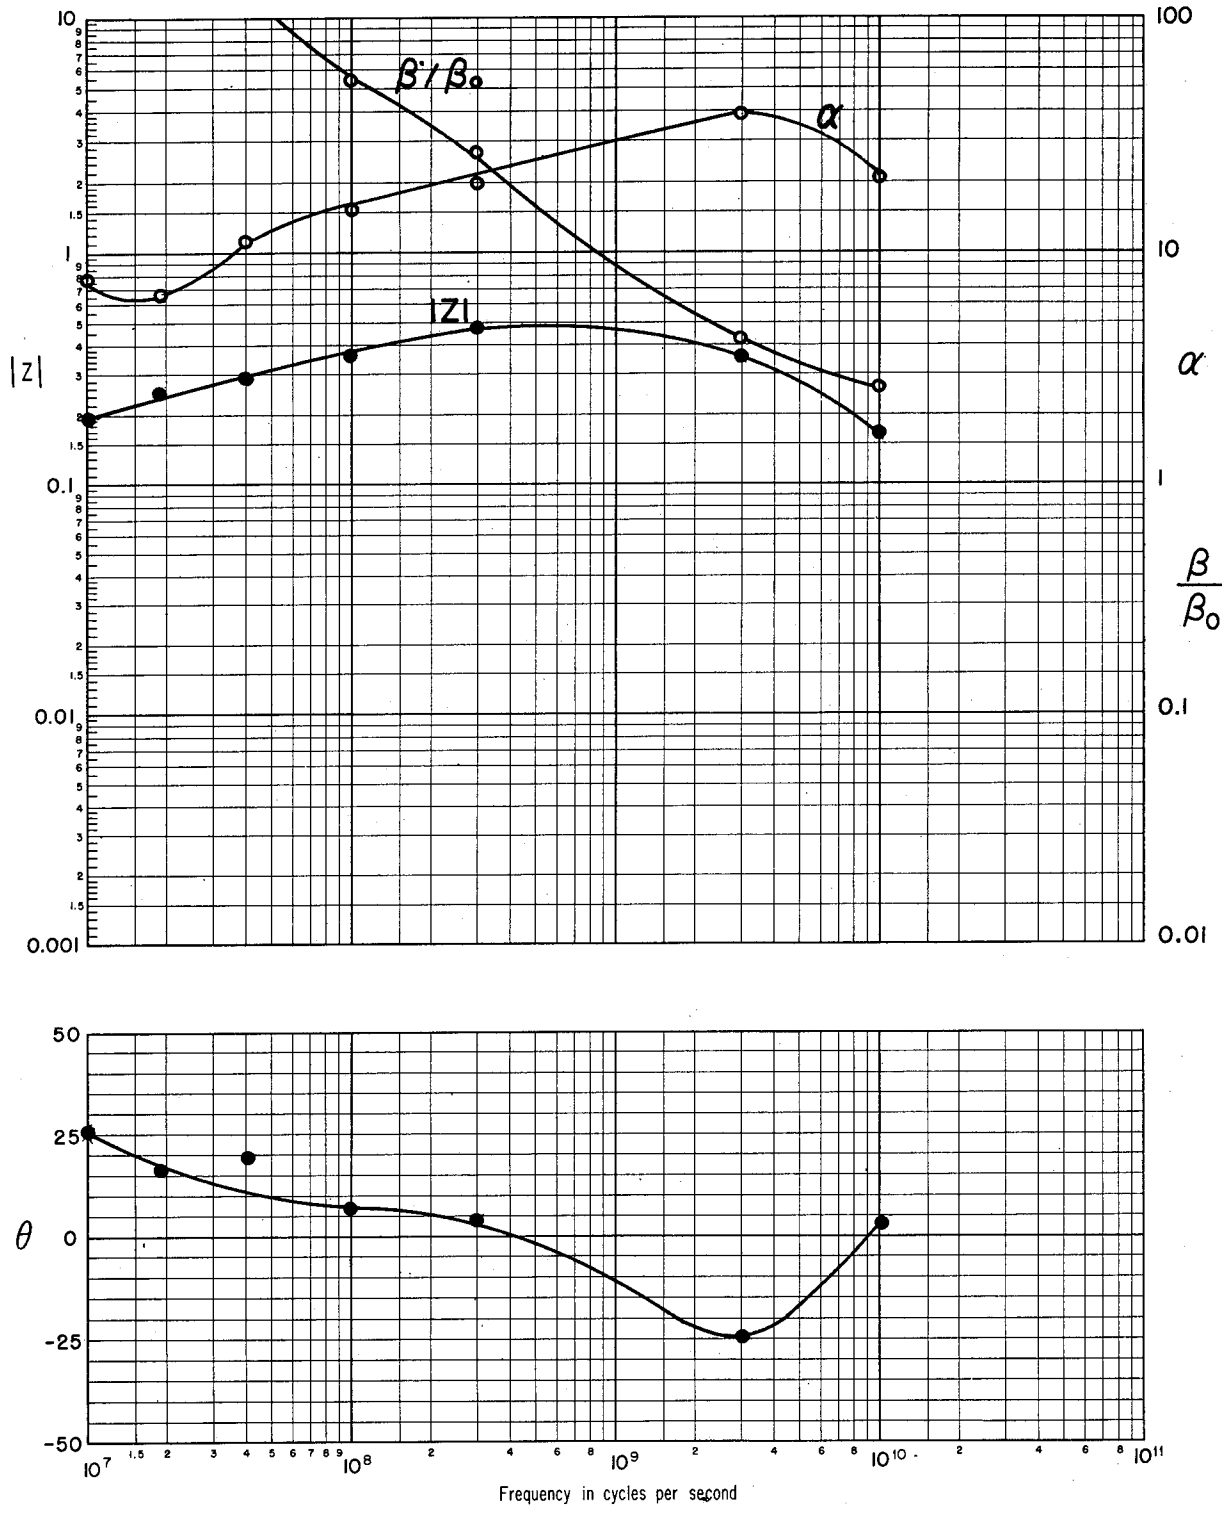

V A. Ferrites


"Ferramic" C — General Ceramics

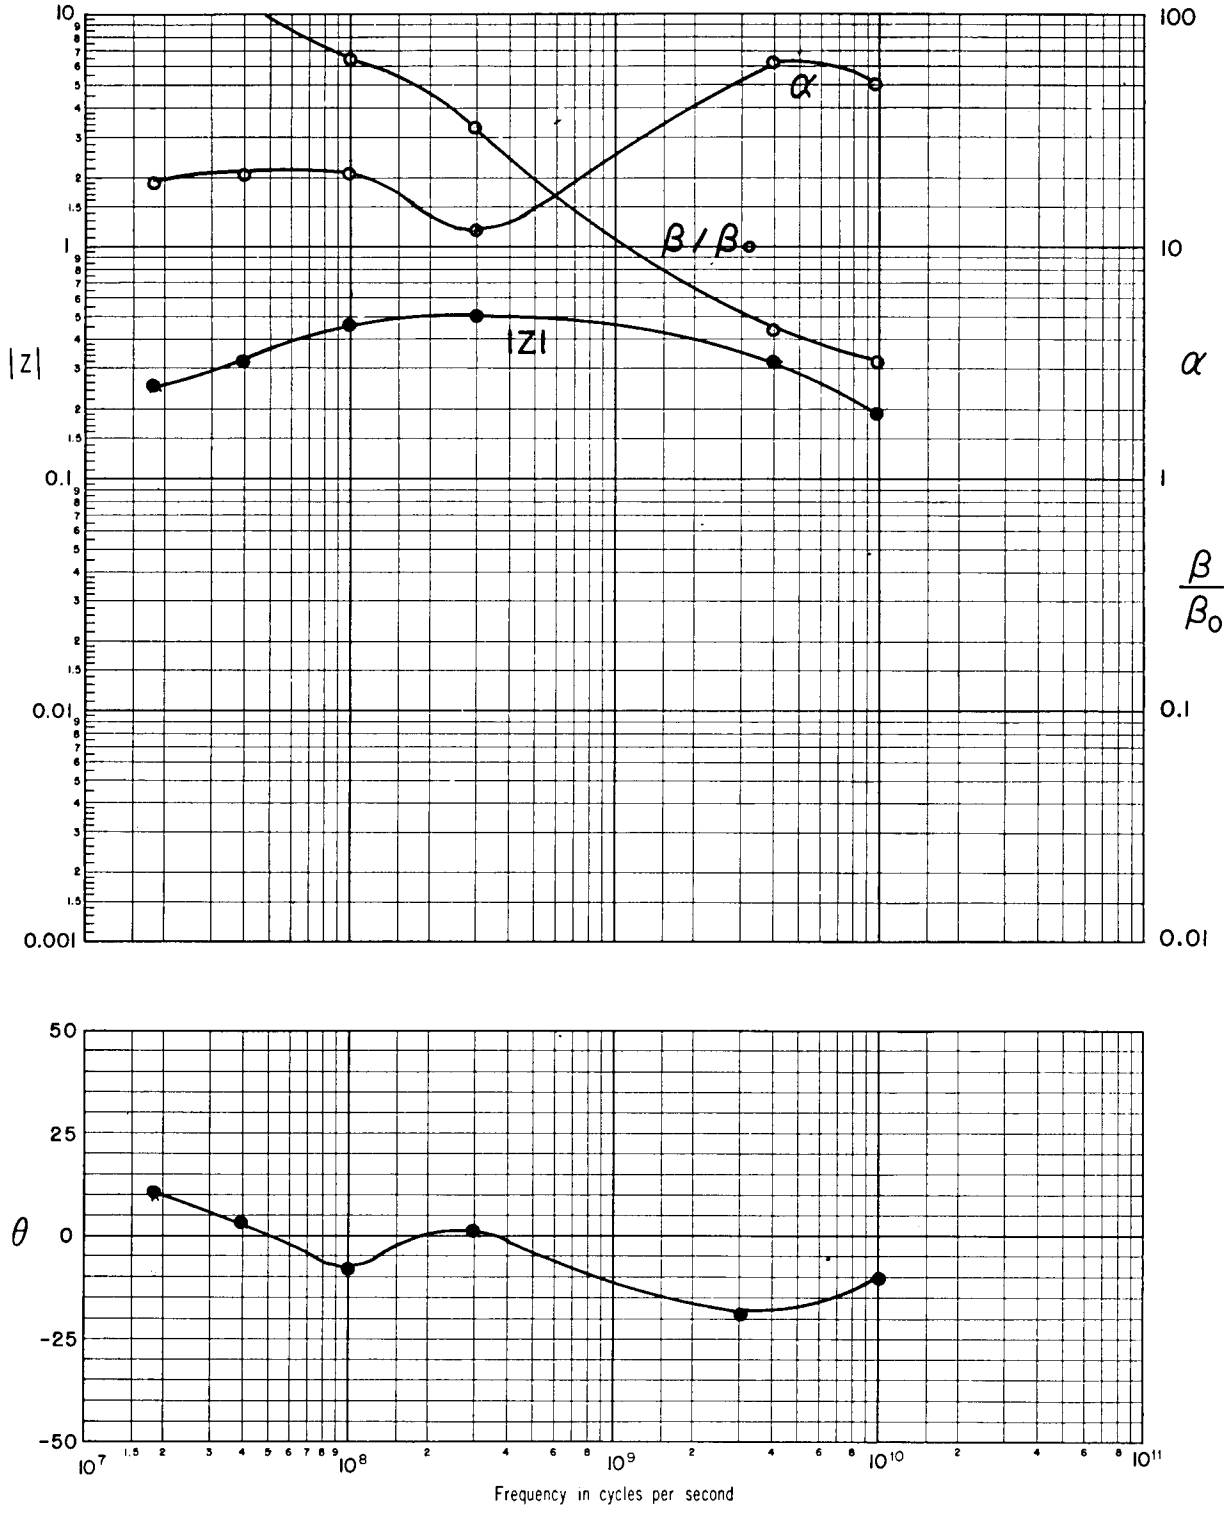


V A. Ferrites

"Ferramic" D


General Ceramics

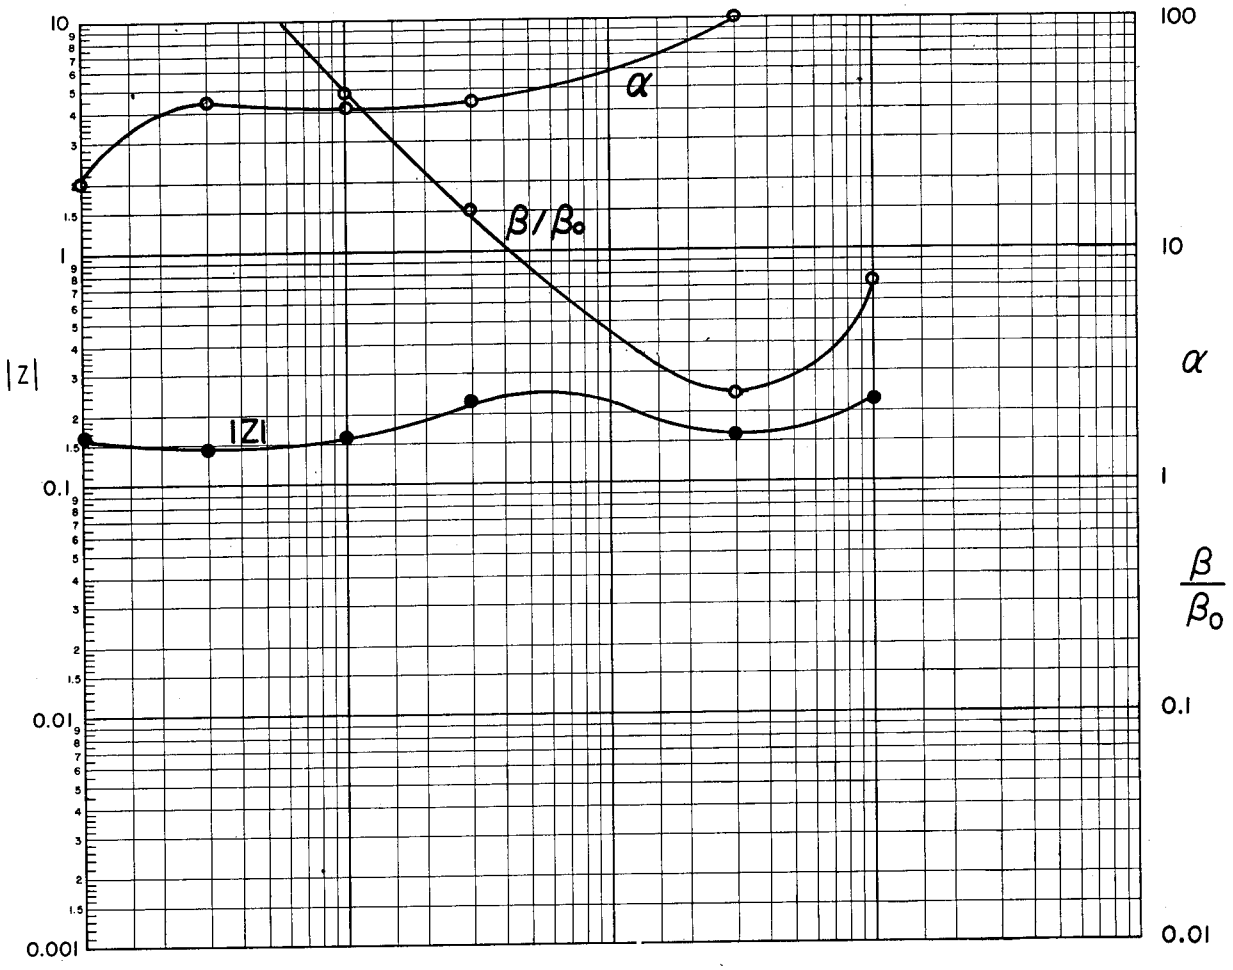

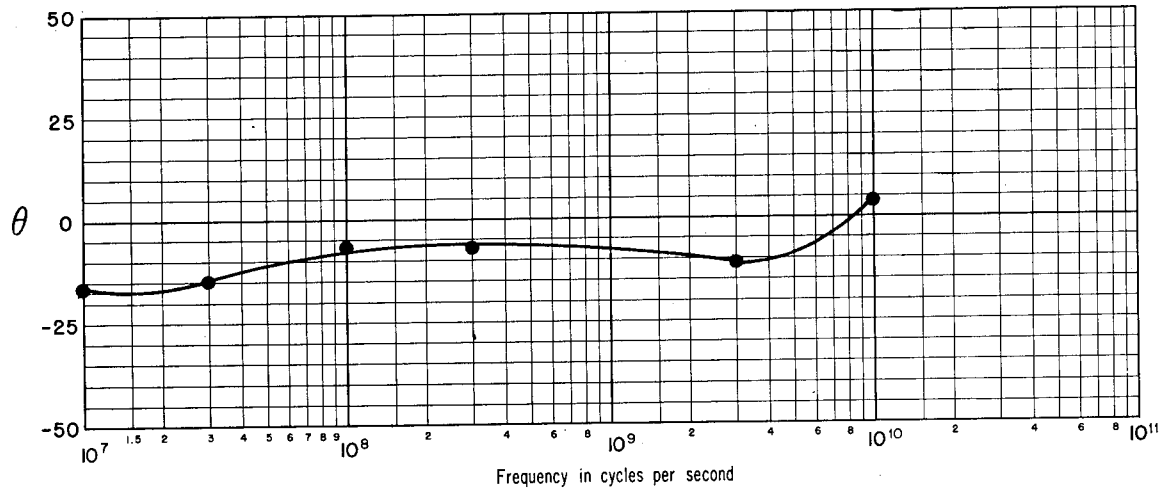


"Ferramic" E

General Ceramics

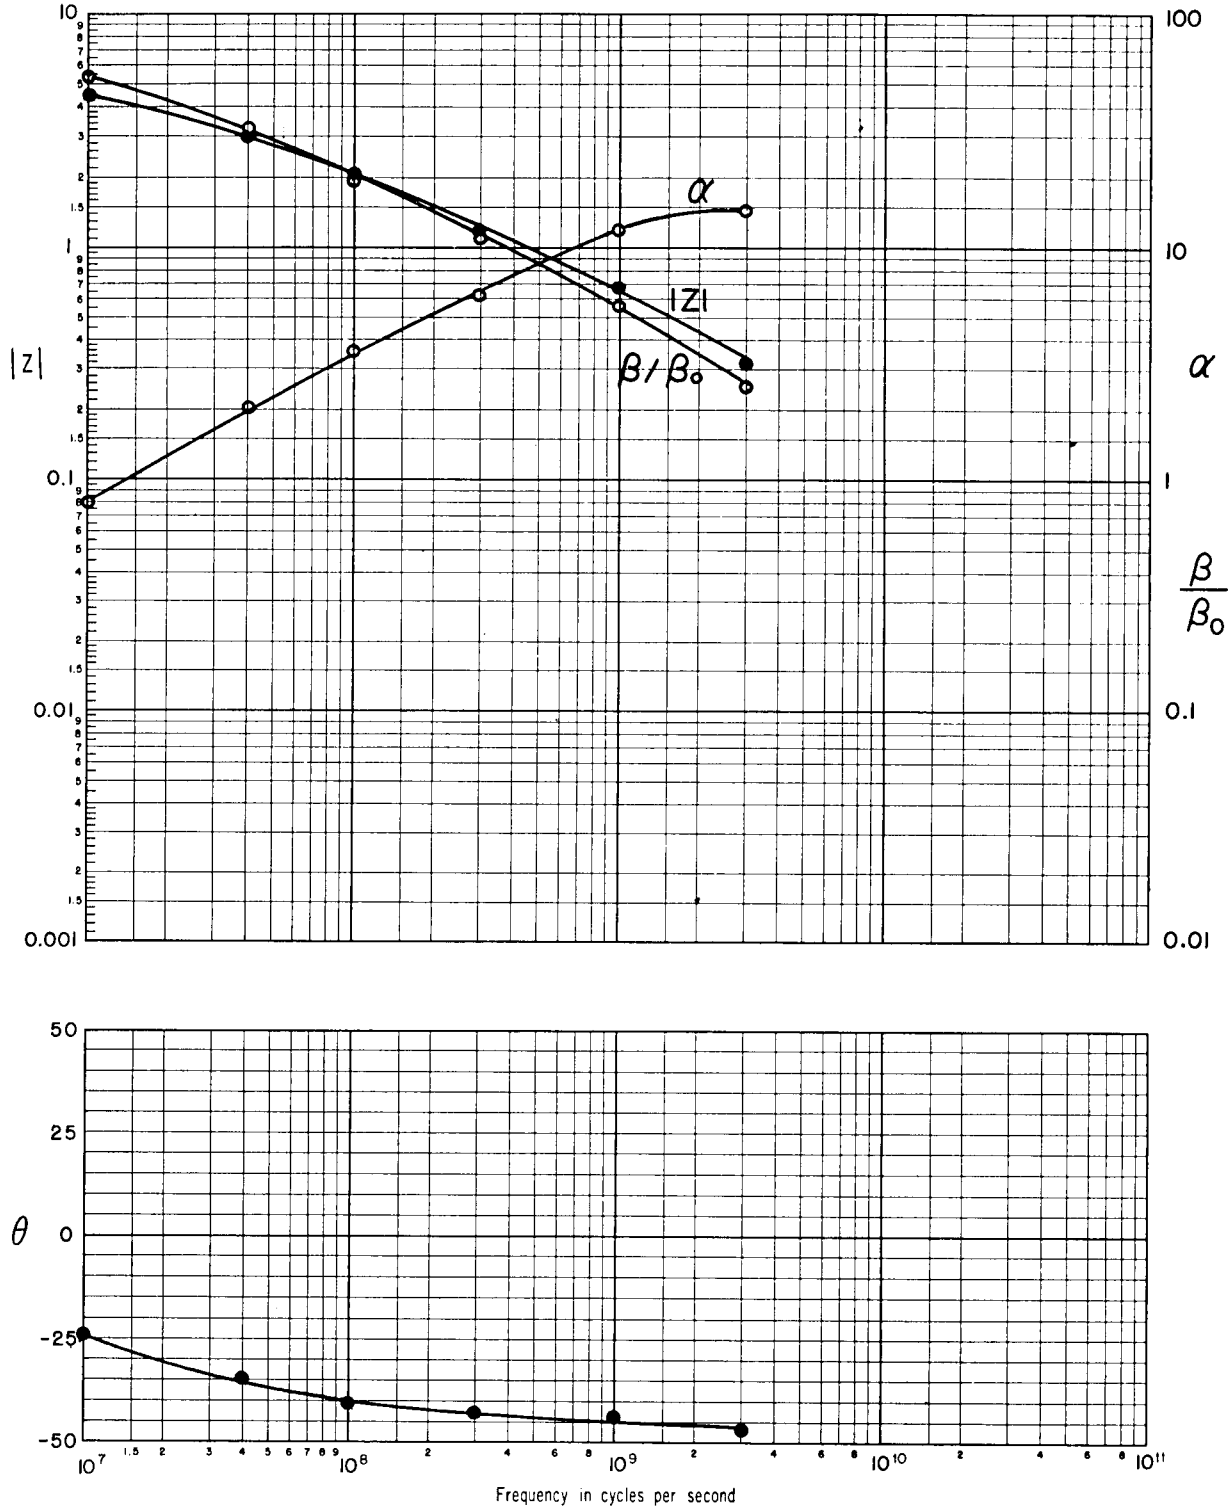

V A. Ferrites


"Ferramic" G — General Ceramics

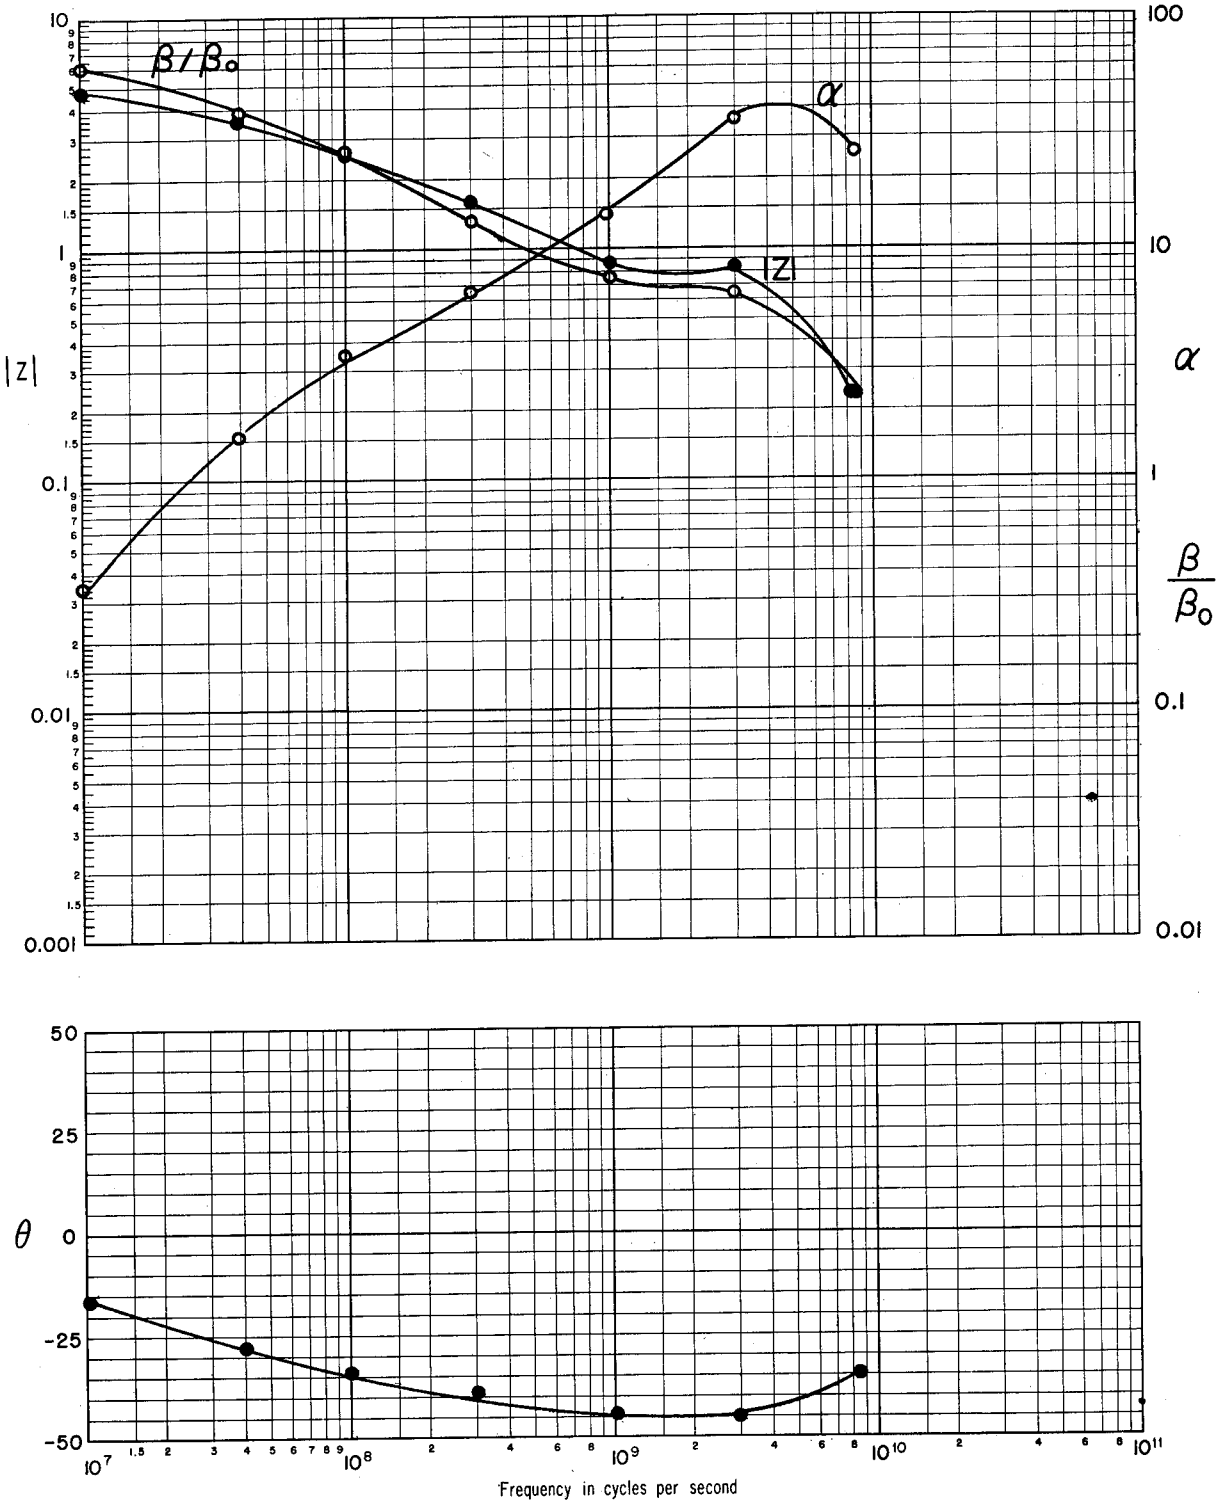

V A. Ferrites


"Ferramic"H

General Ceramics

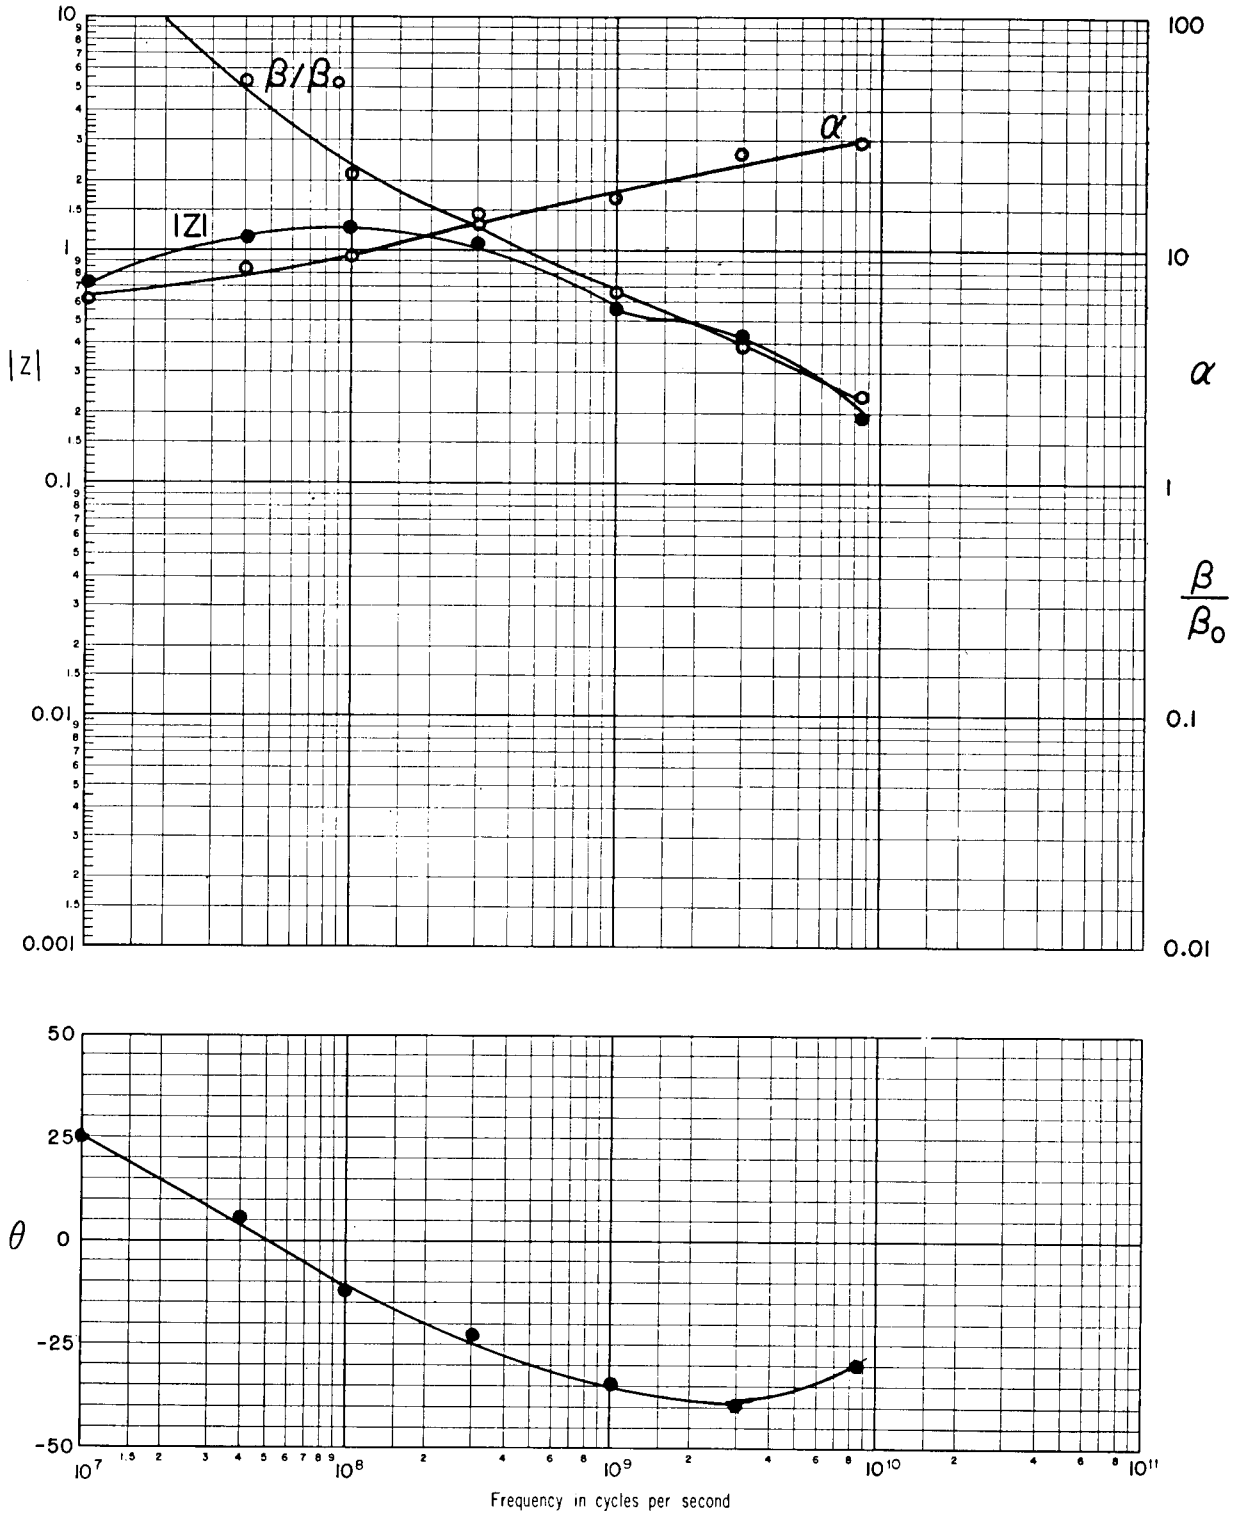


"Ferramic" I

General Ceramics

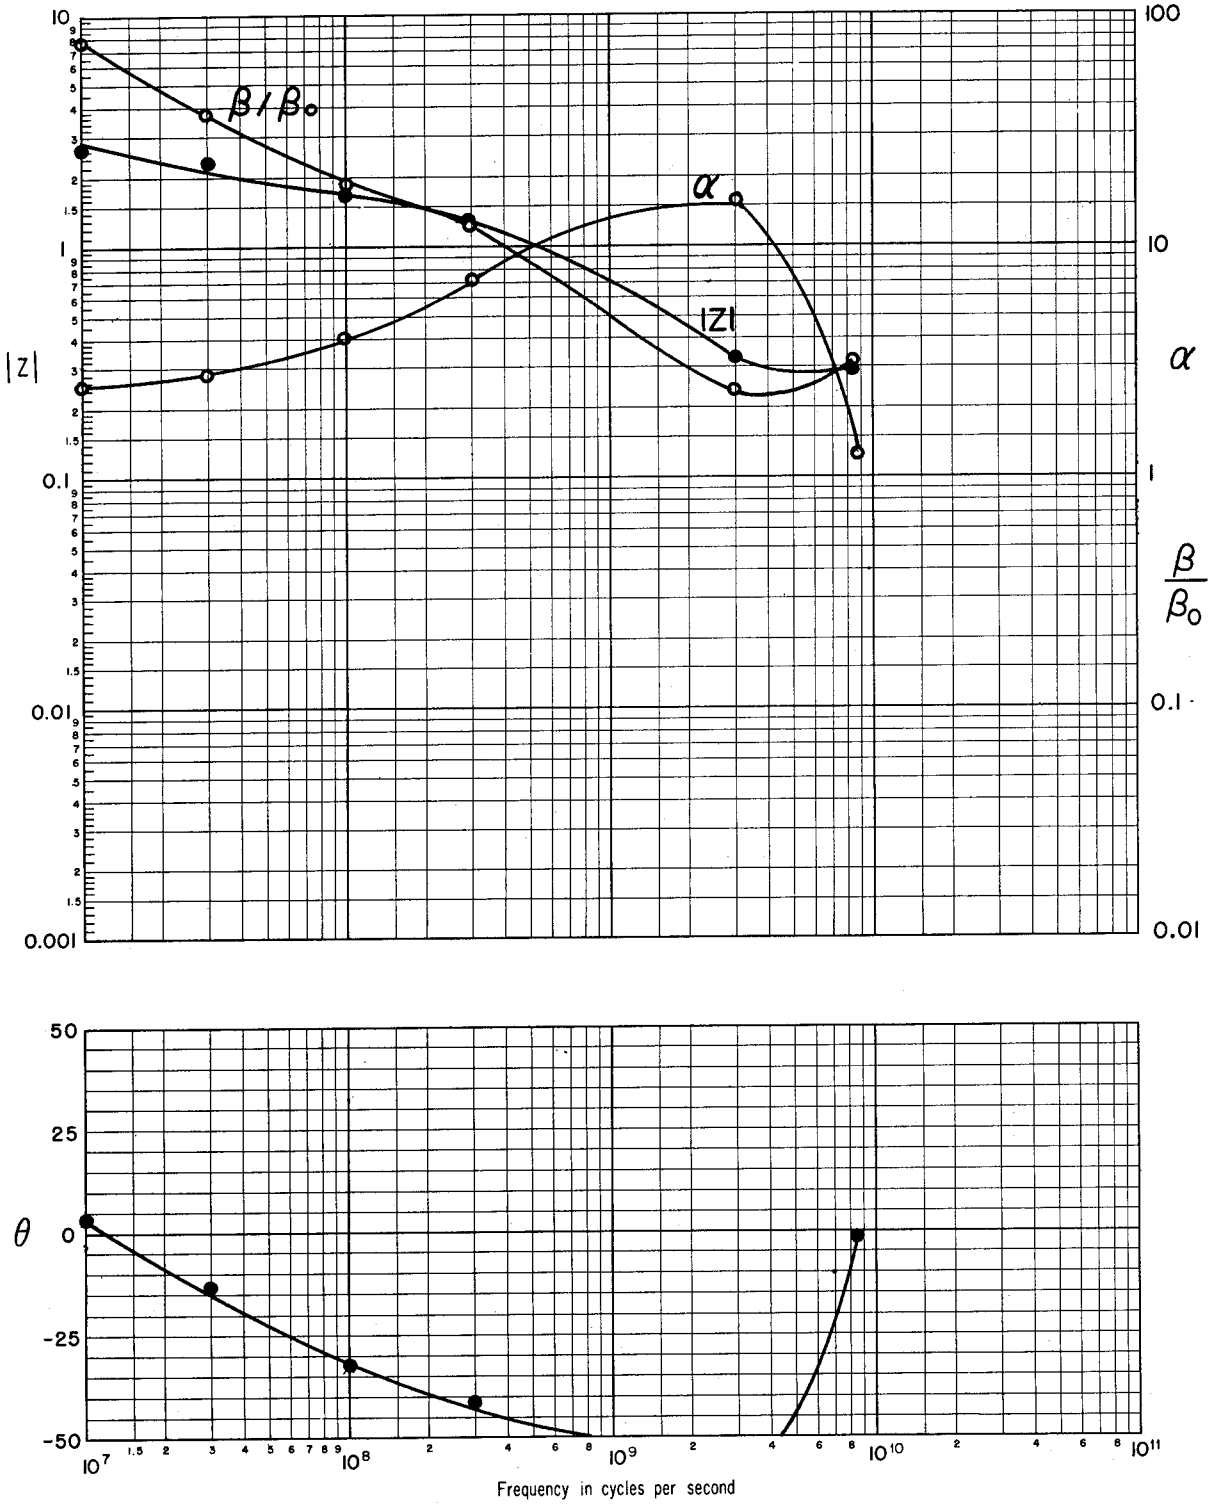


"Ferramic" J

General Ceramics

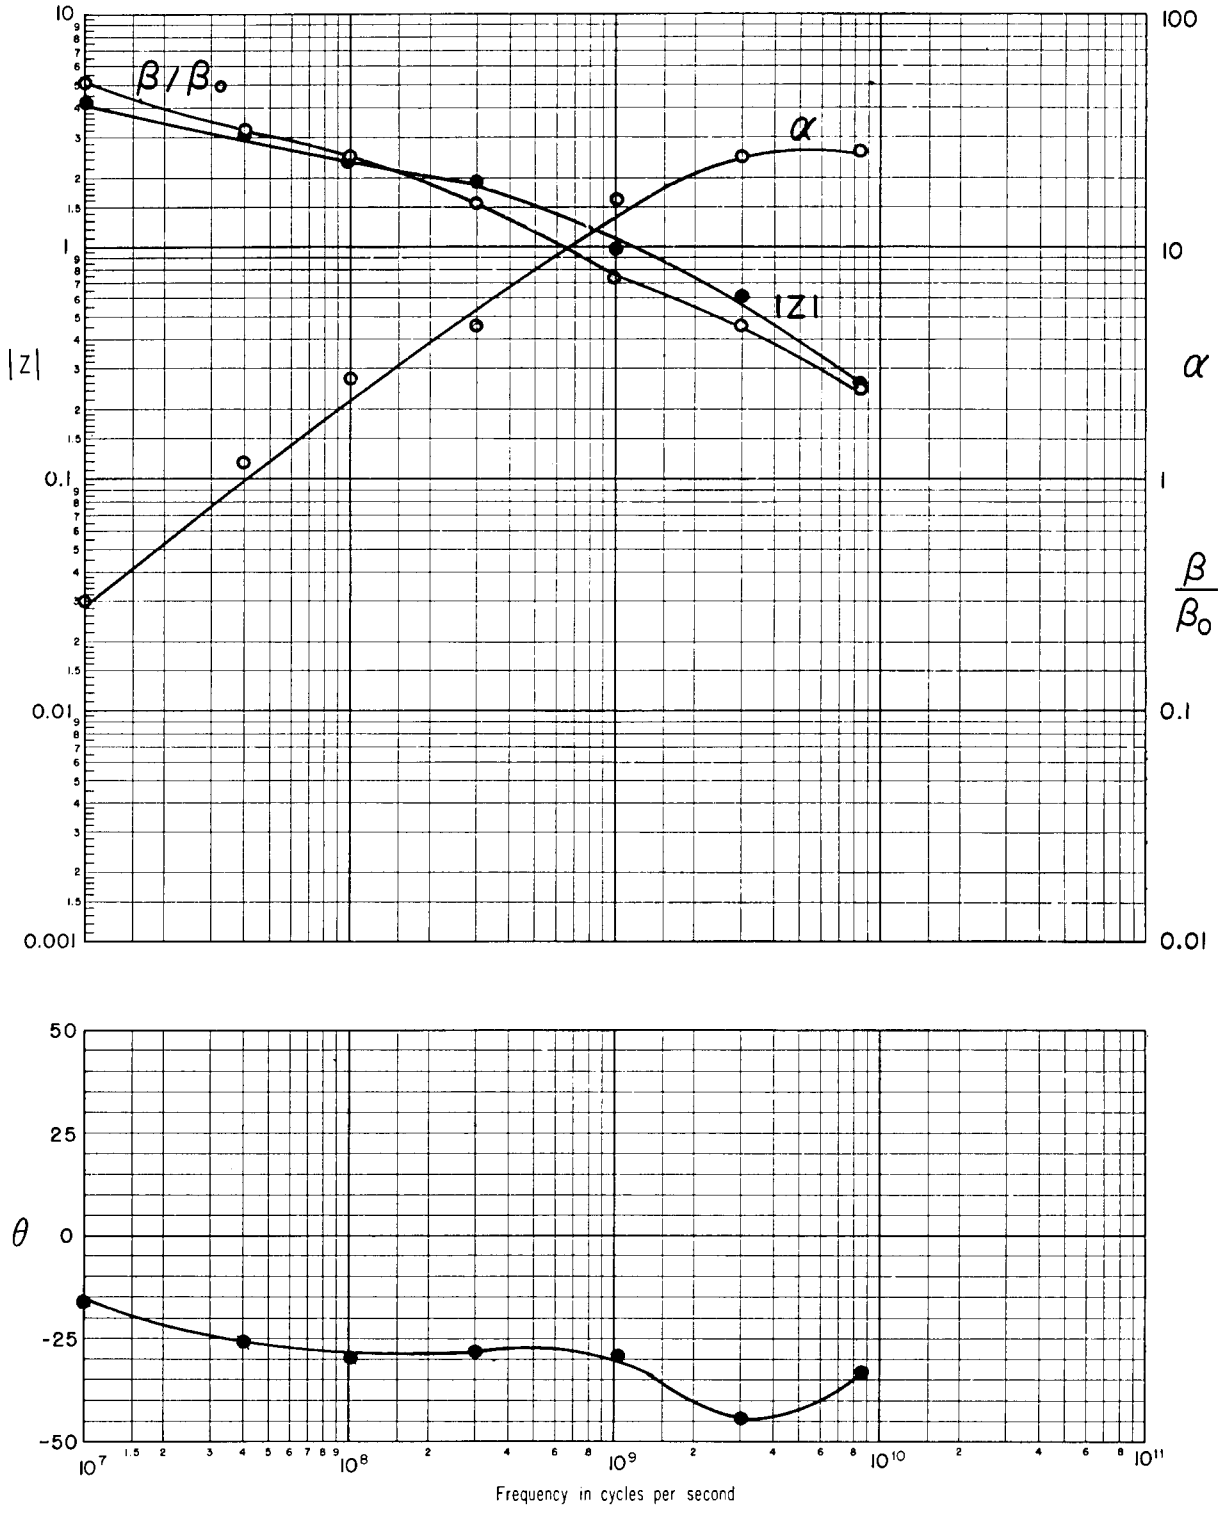


"Ferramic" K

General Ceramics

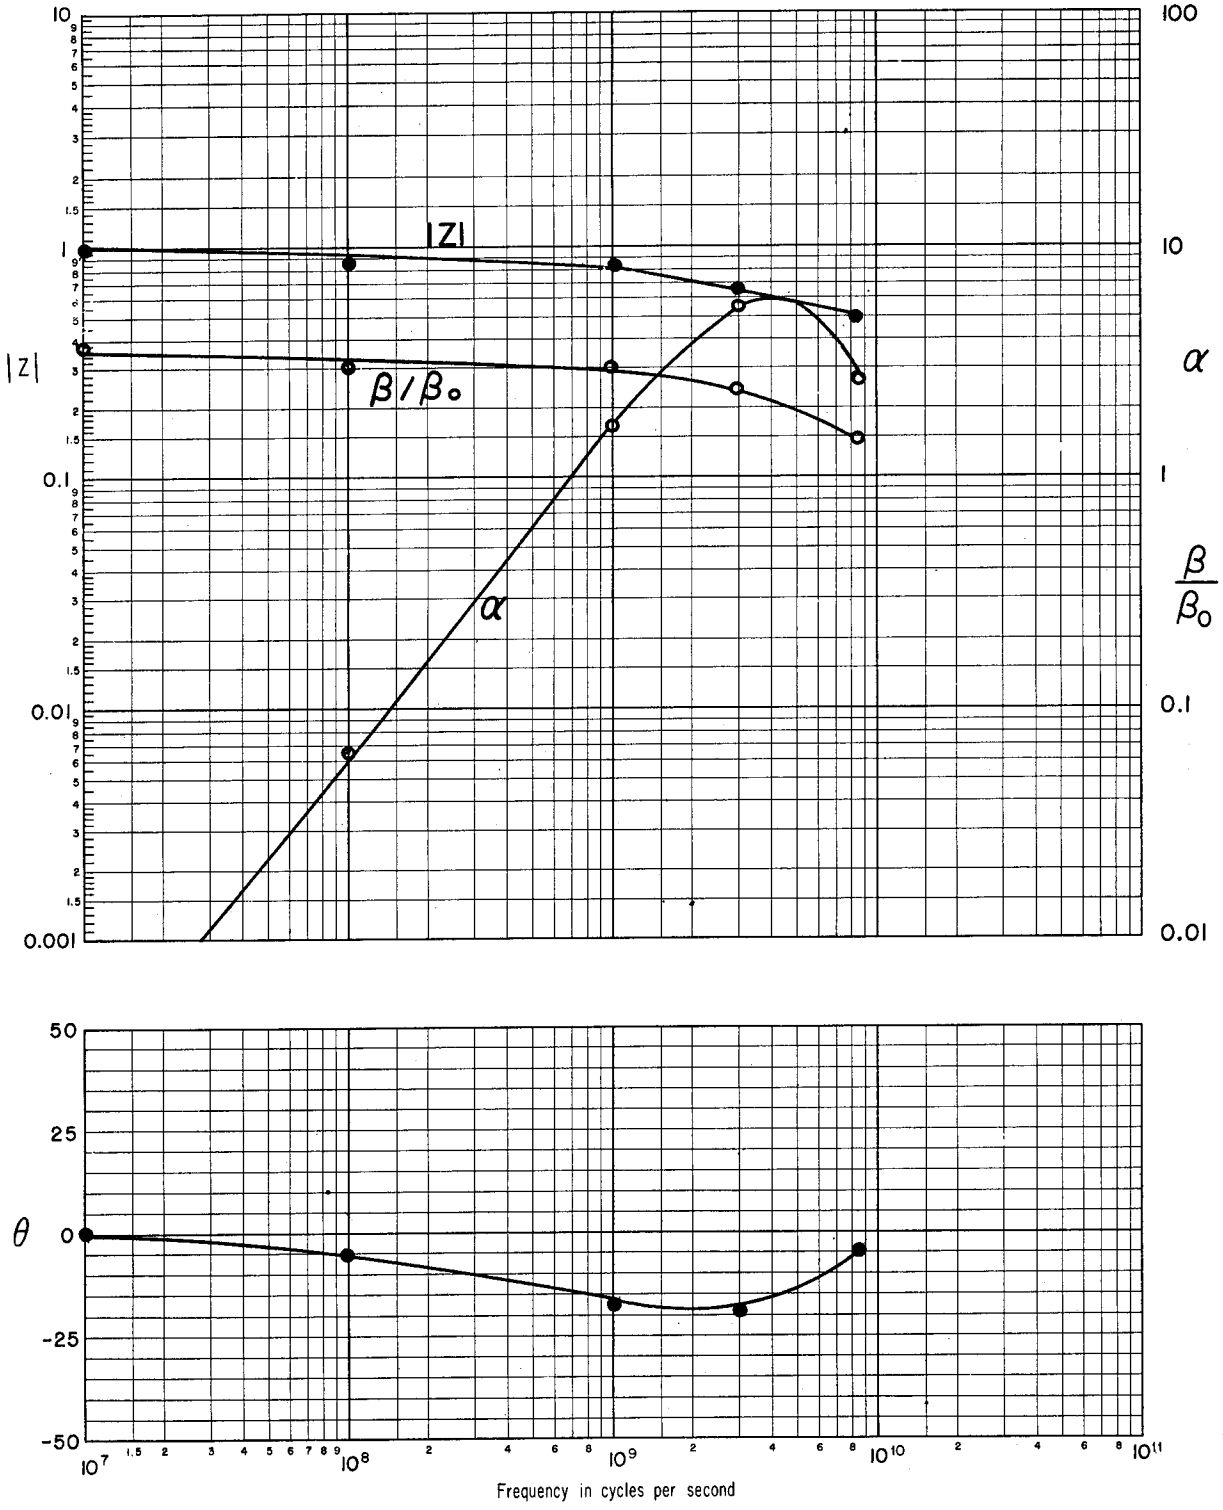



V A. Ferrites

"Ferramic"Q (rec'd Dec. 1953) General Ceramics

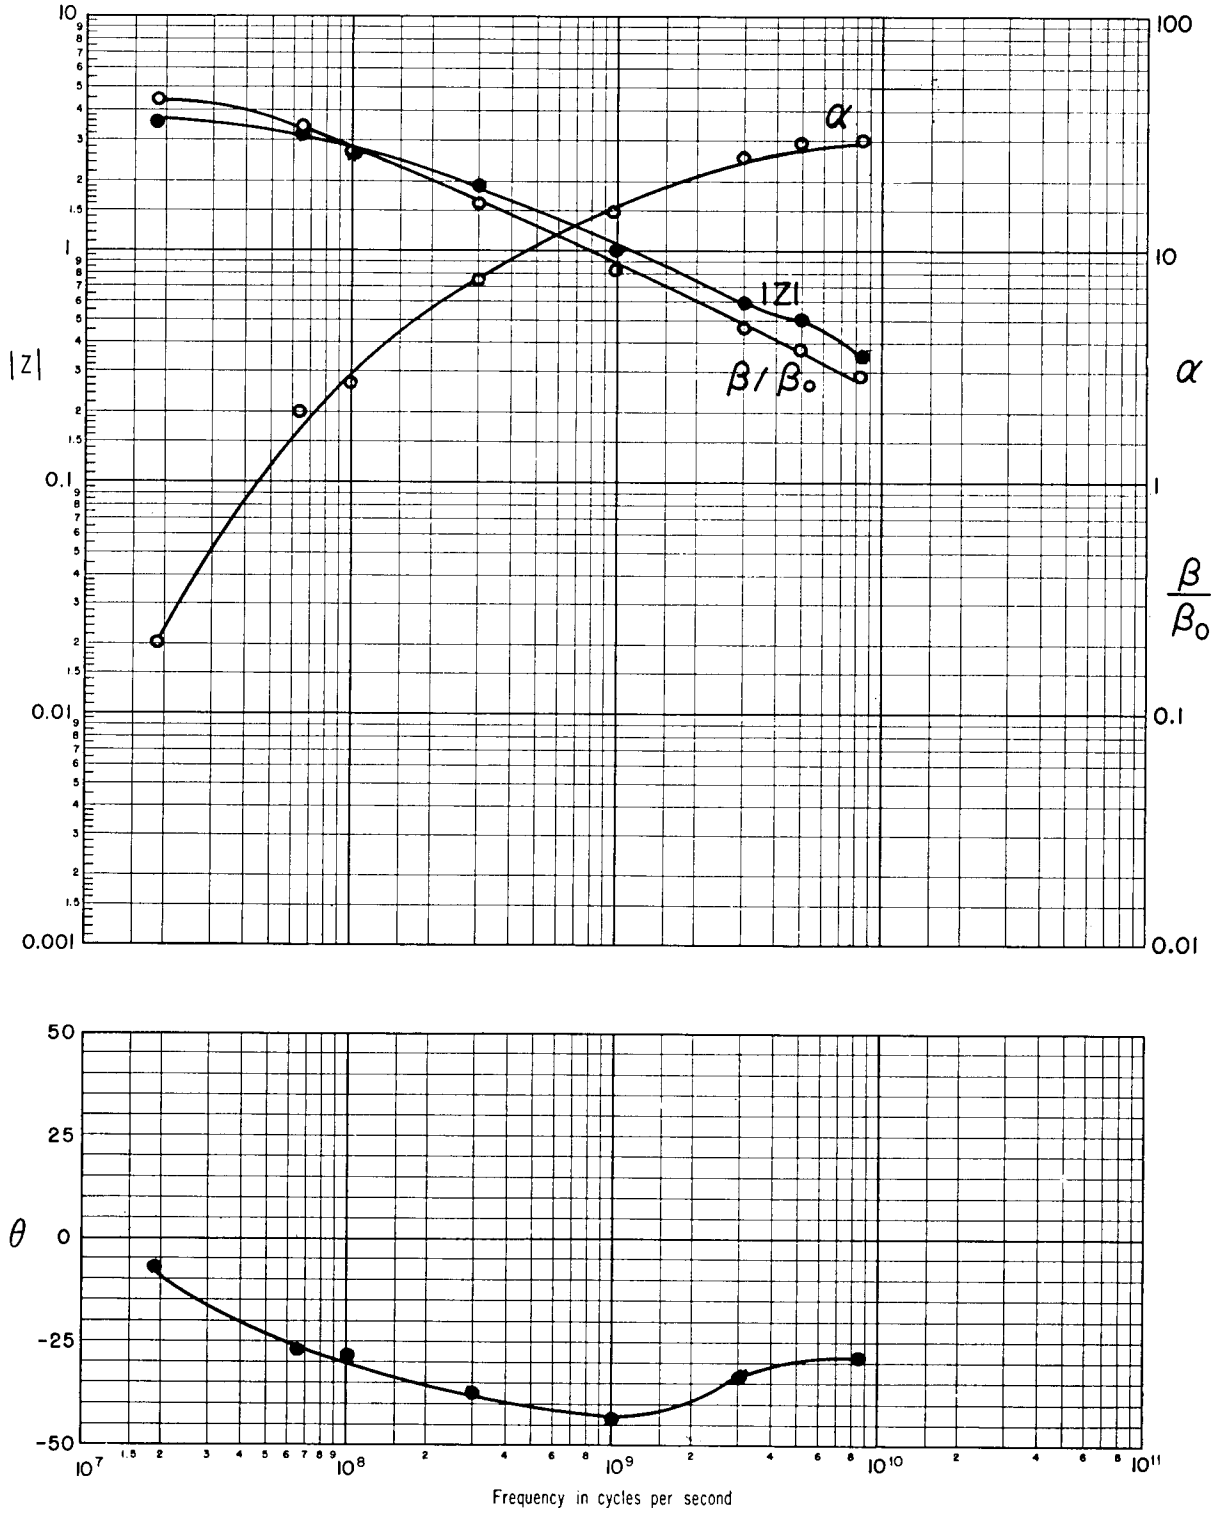


"Ferramic" Q (Aug. 1954) General Ceramics

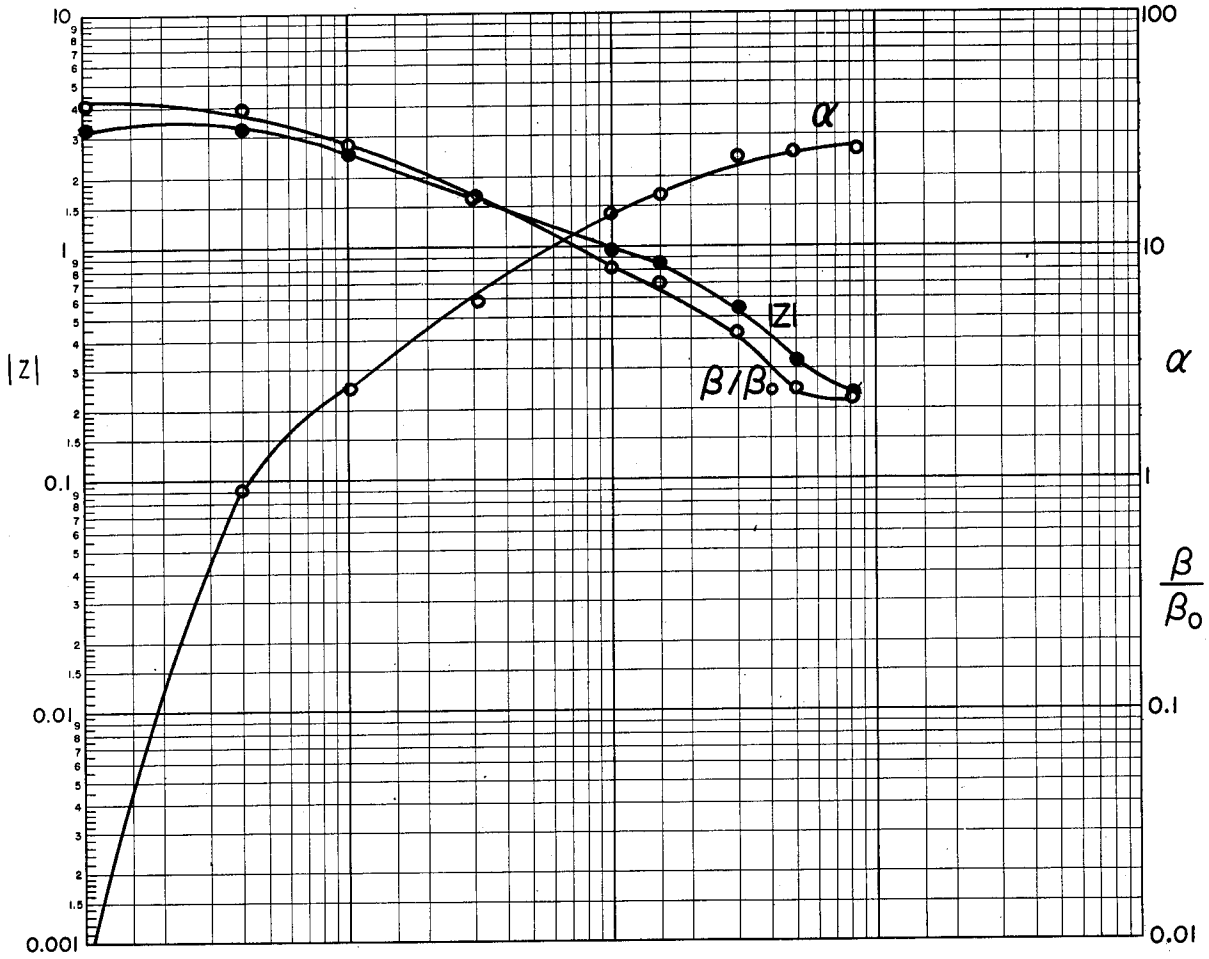


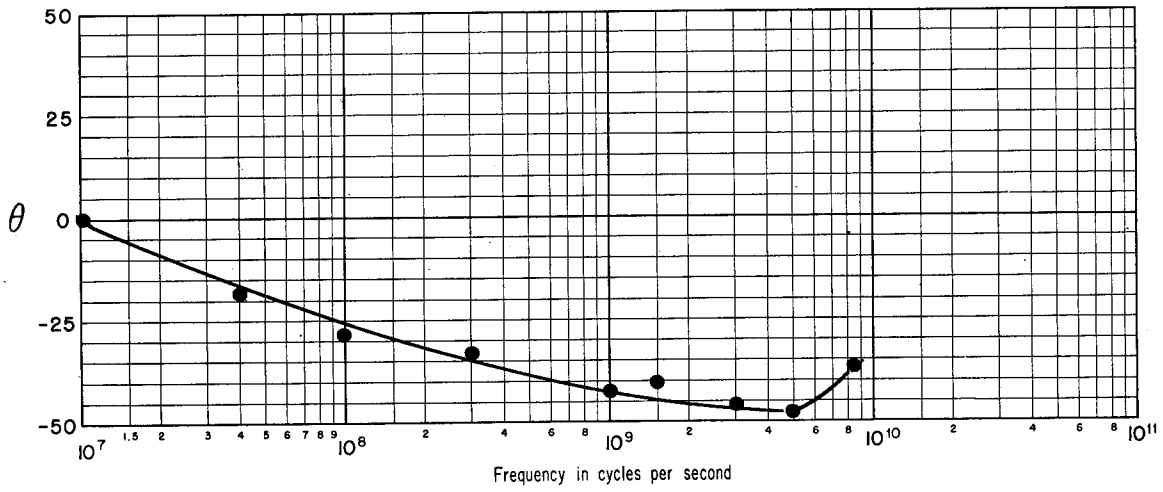


"Ferramic" 1118 General Ceramics

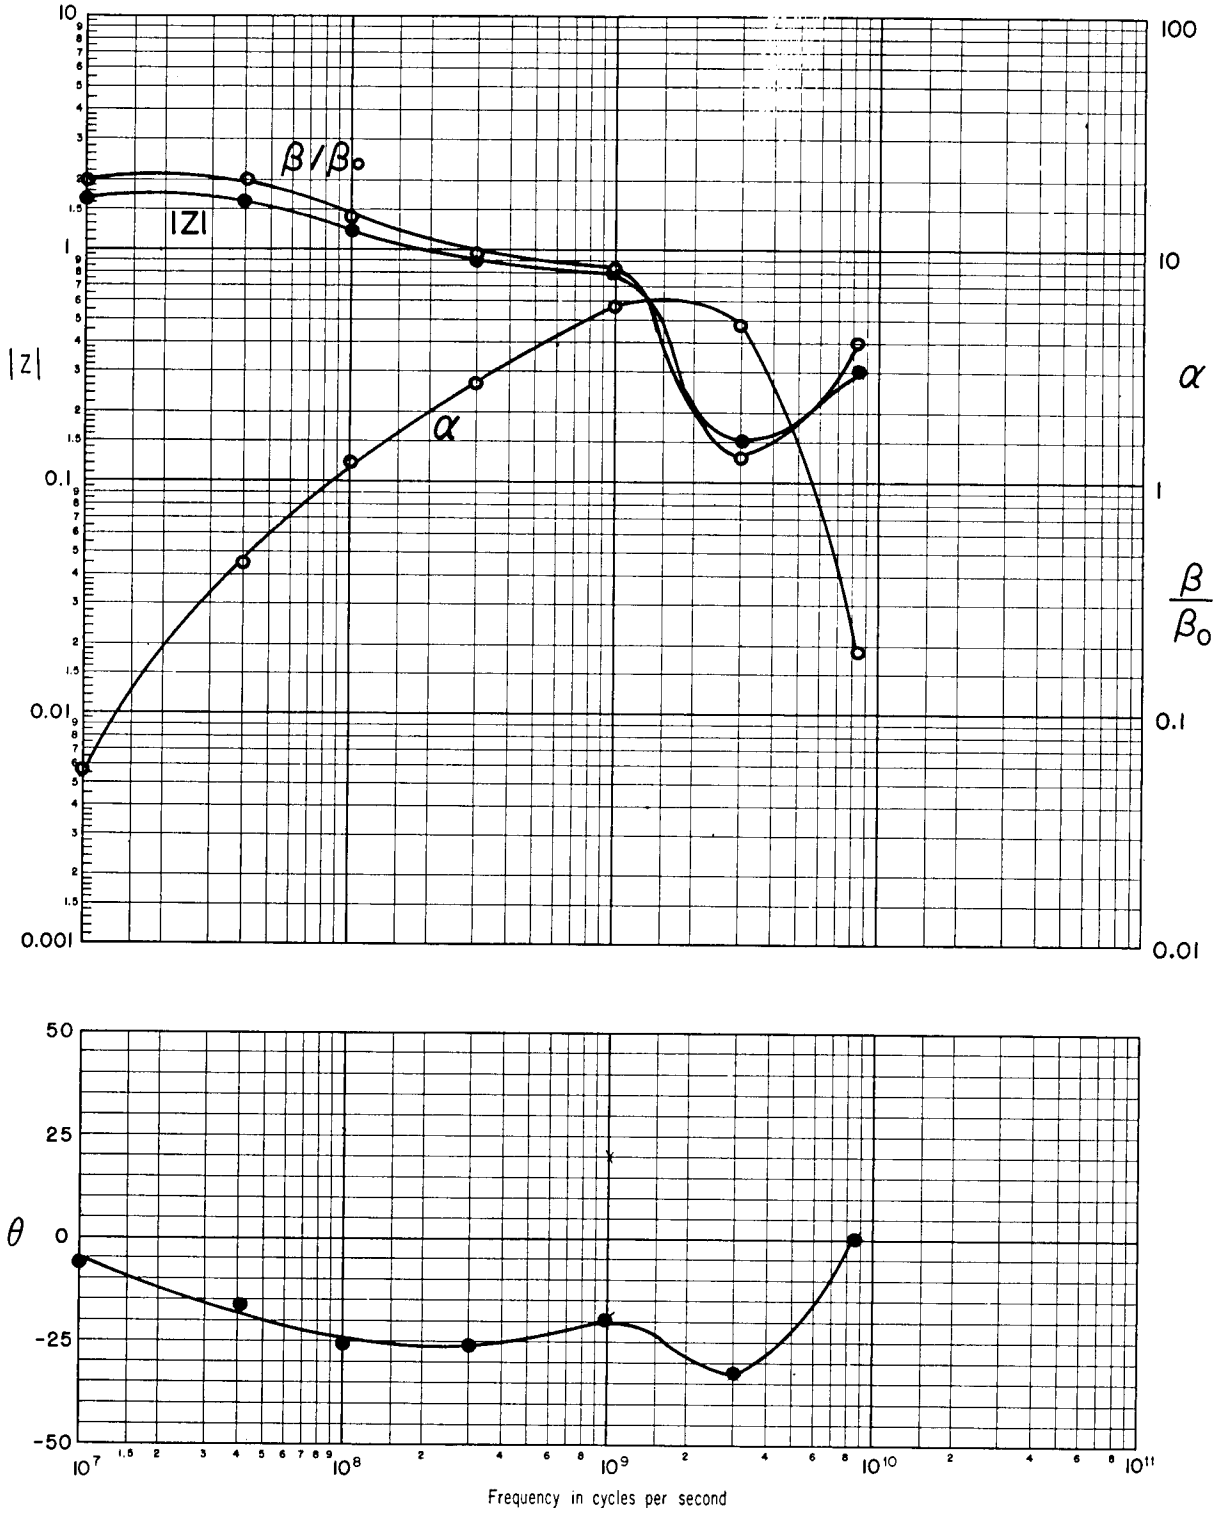


"Ferramic" 1331 General Ceramics

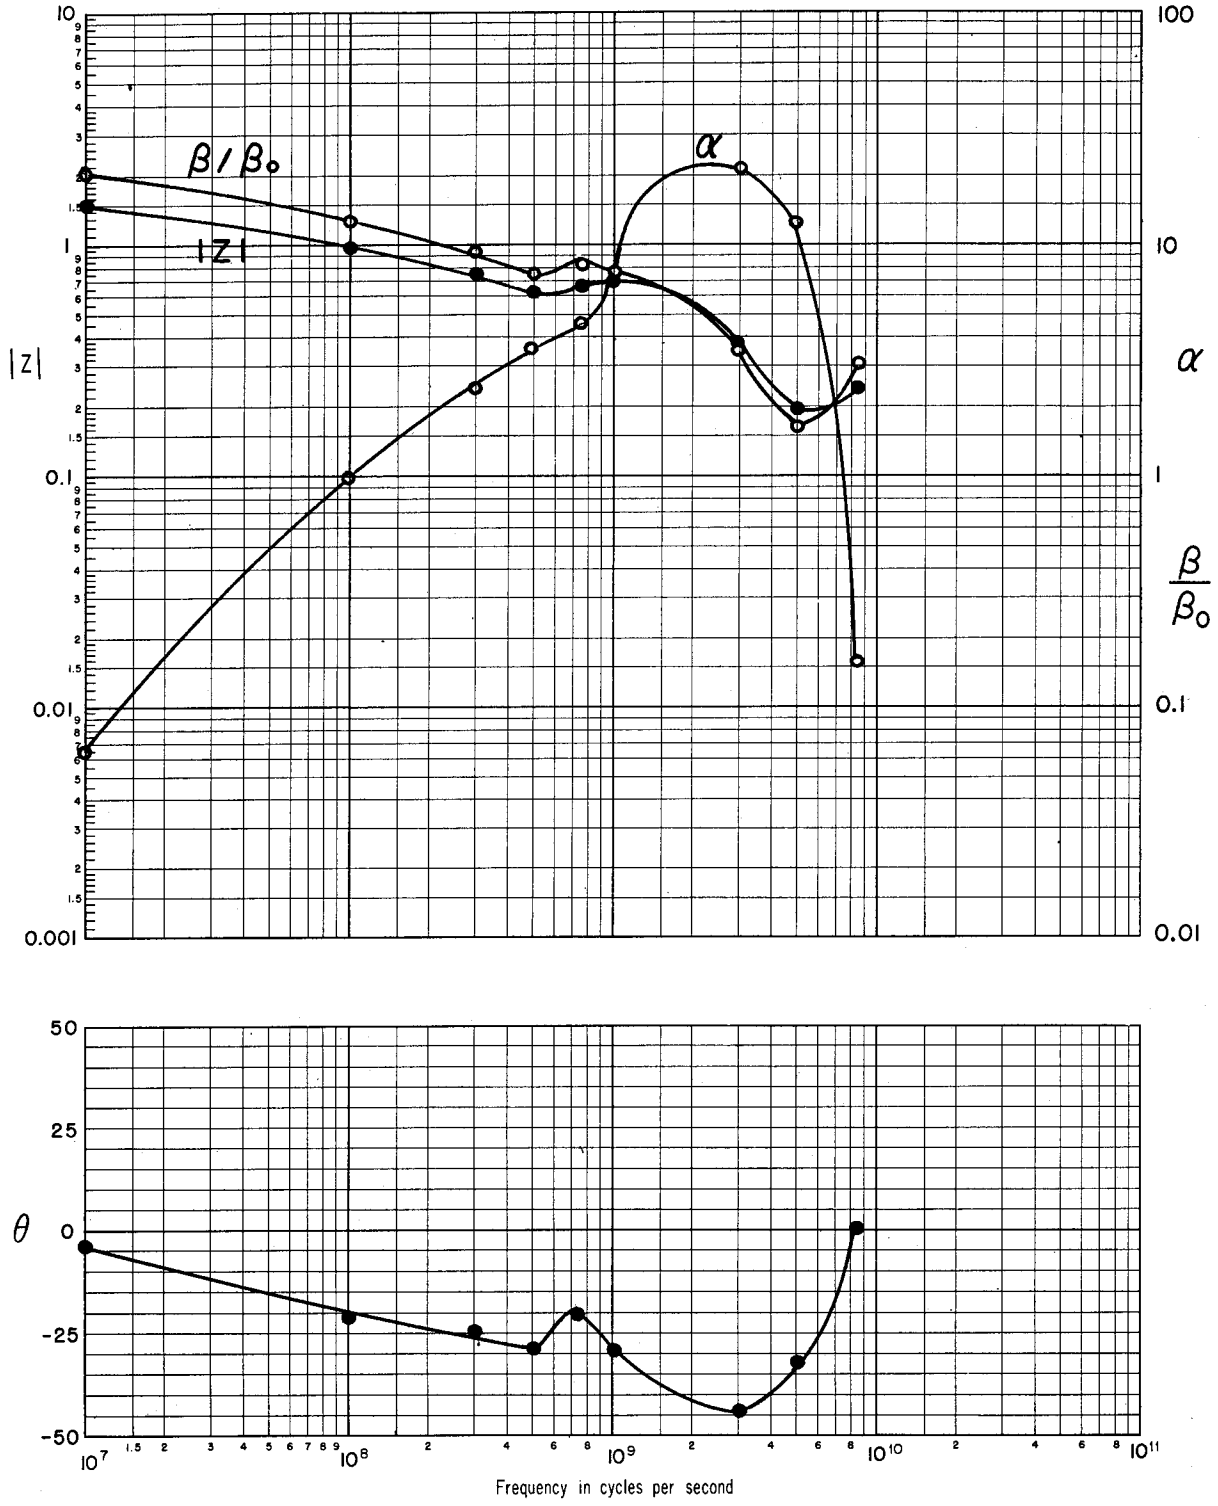


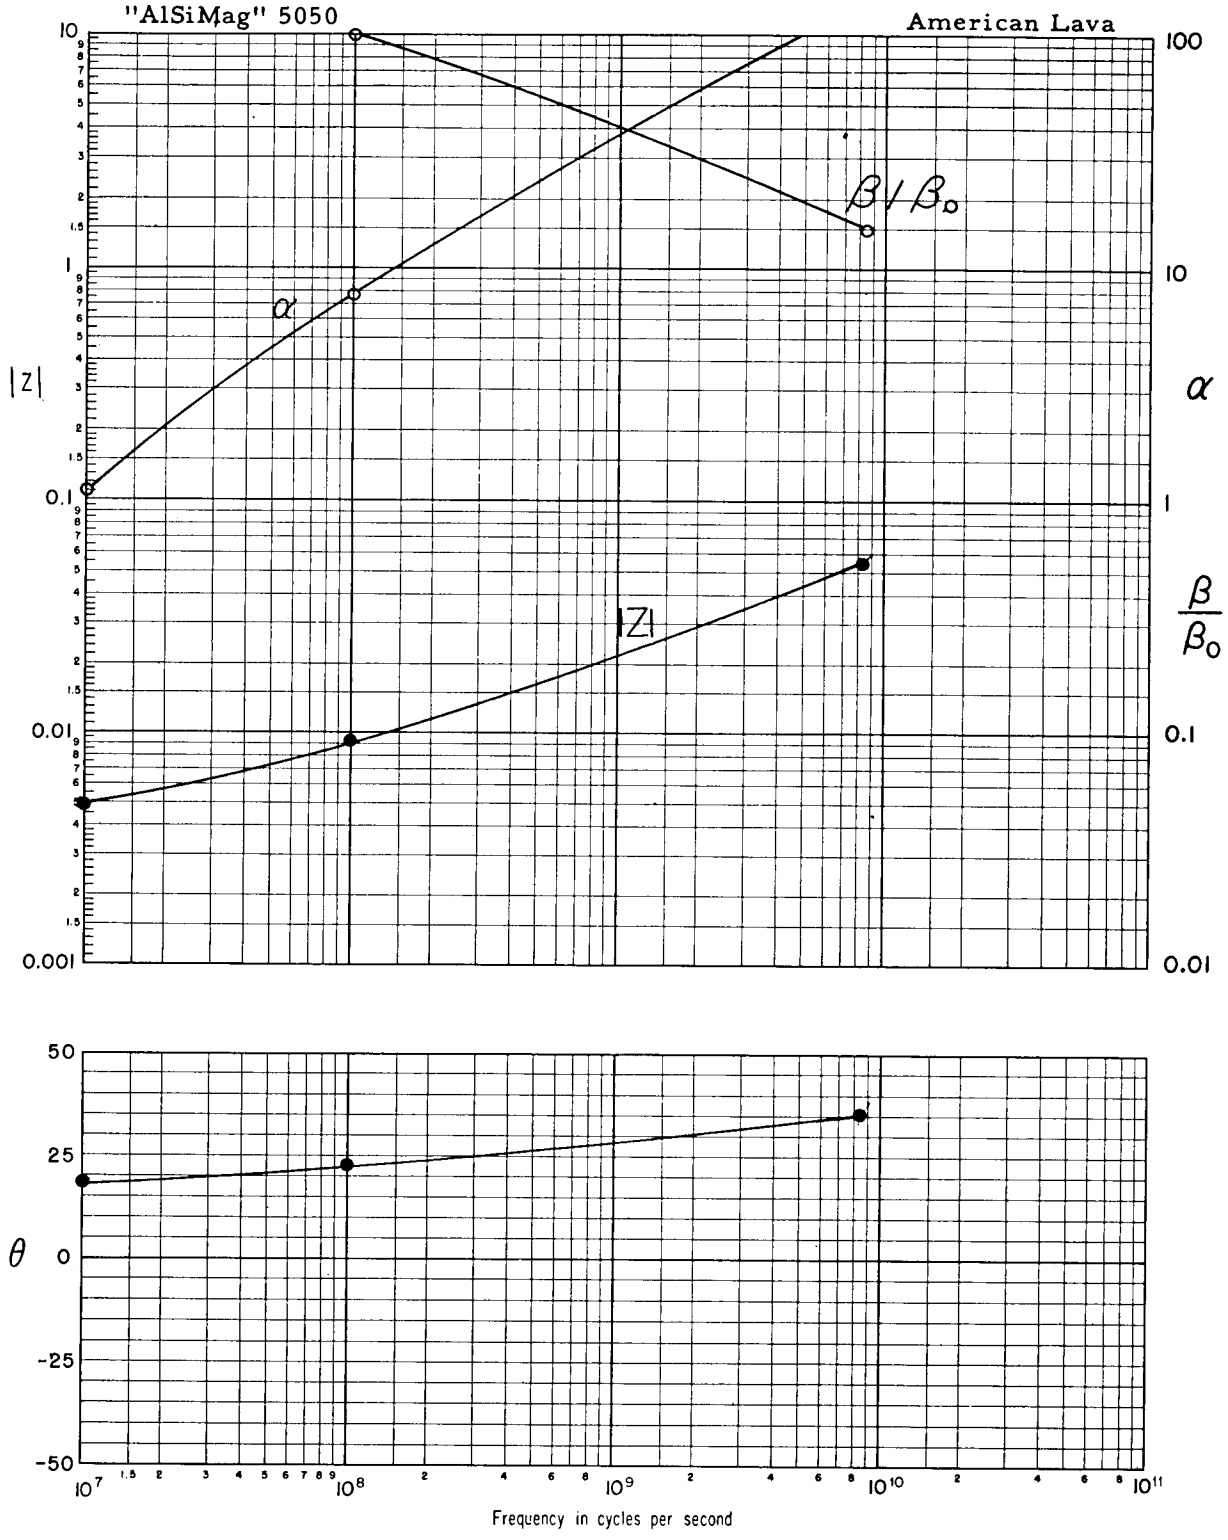
"AlSiMag" 5050
American Lava
|Z|
α
β/β₀
|Z|
α
β/β₀
θ
Frequency in cycles per second

V A. Conducting Plastics

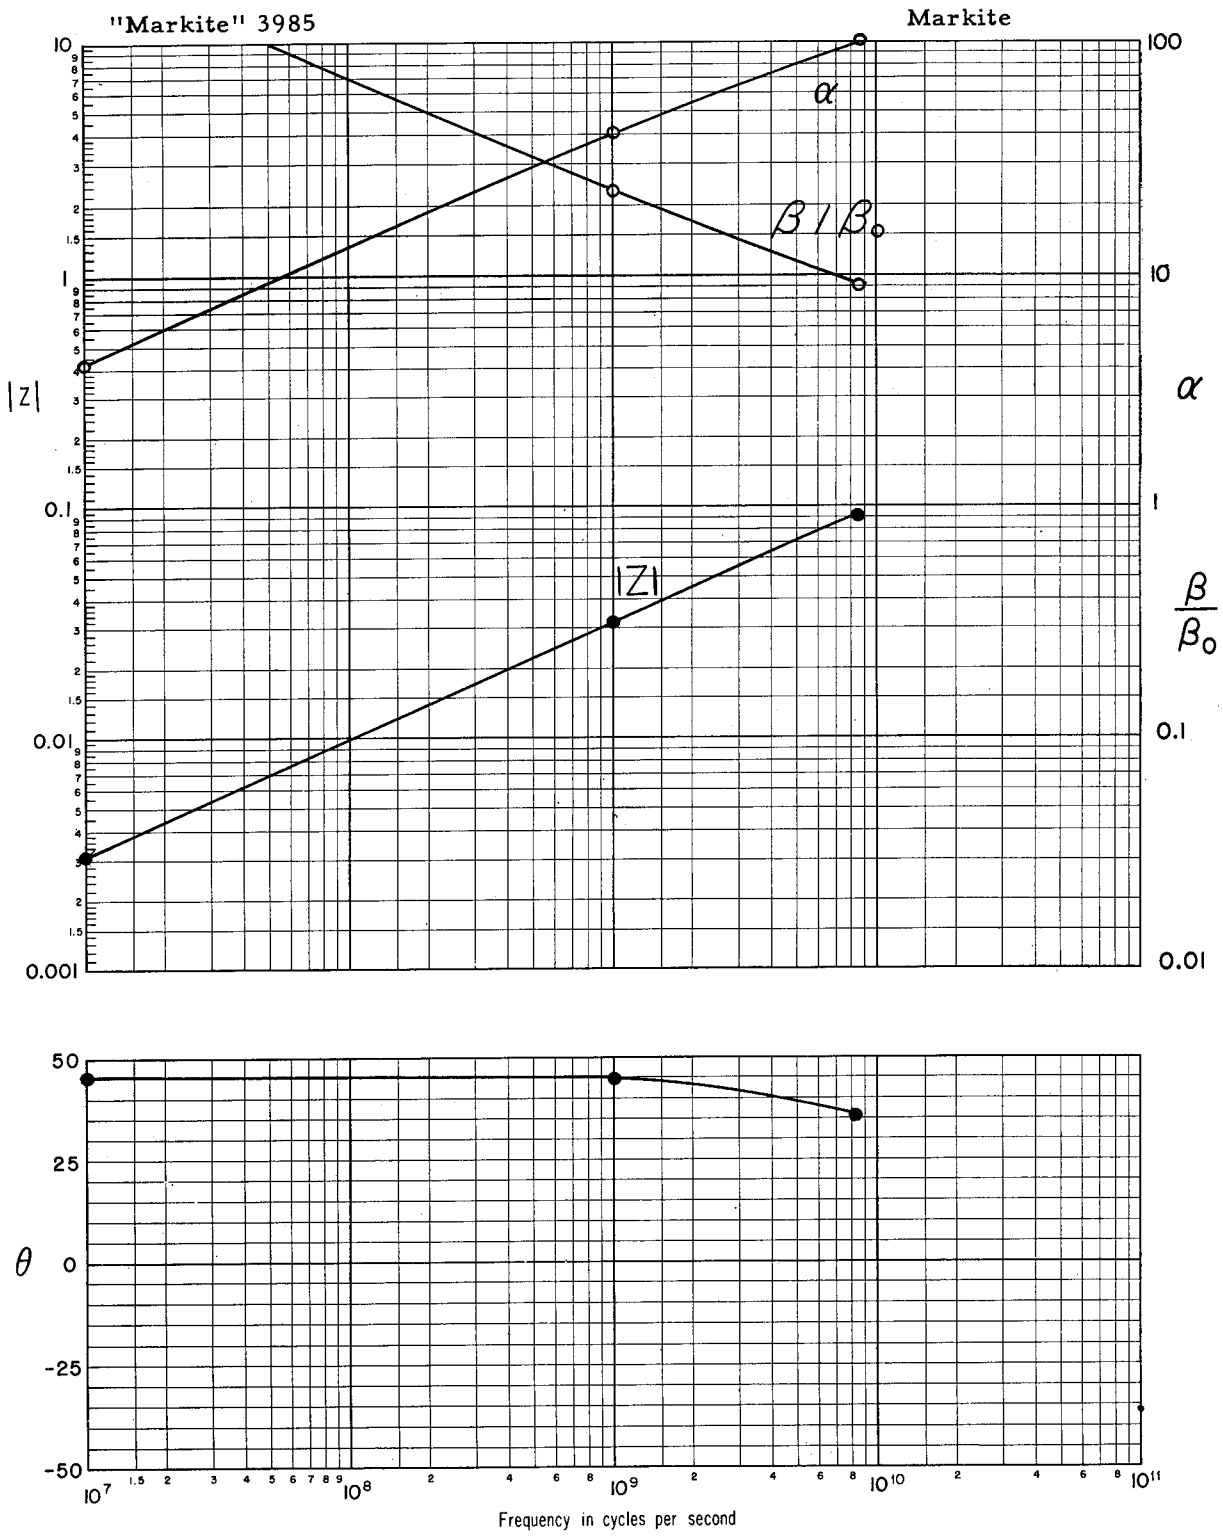


V C. Conducting Plastics

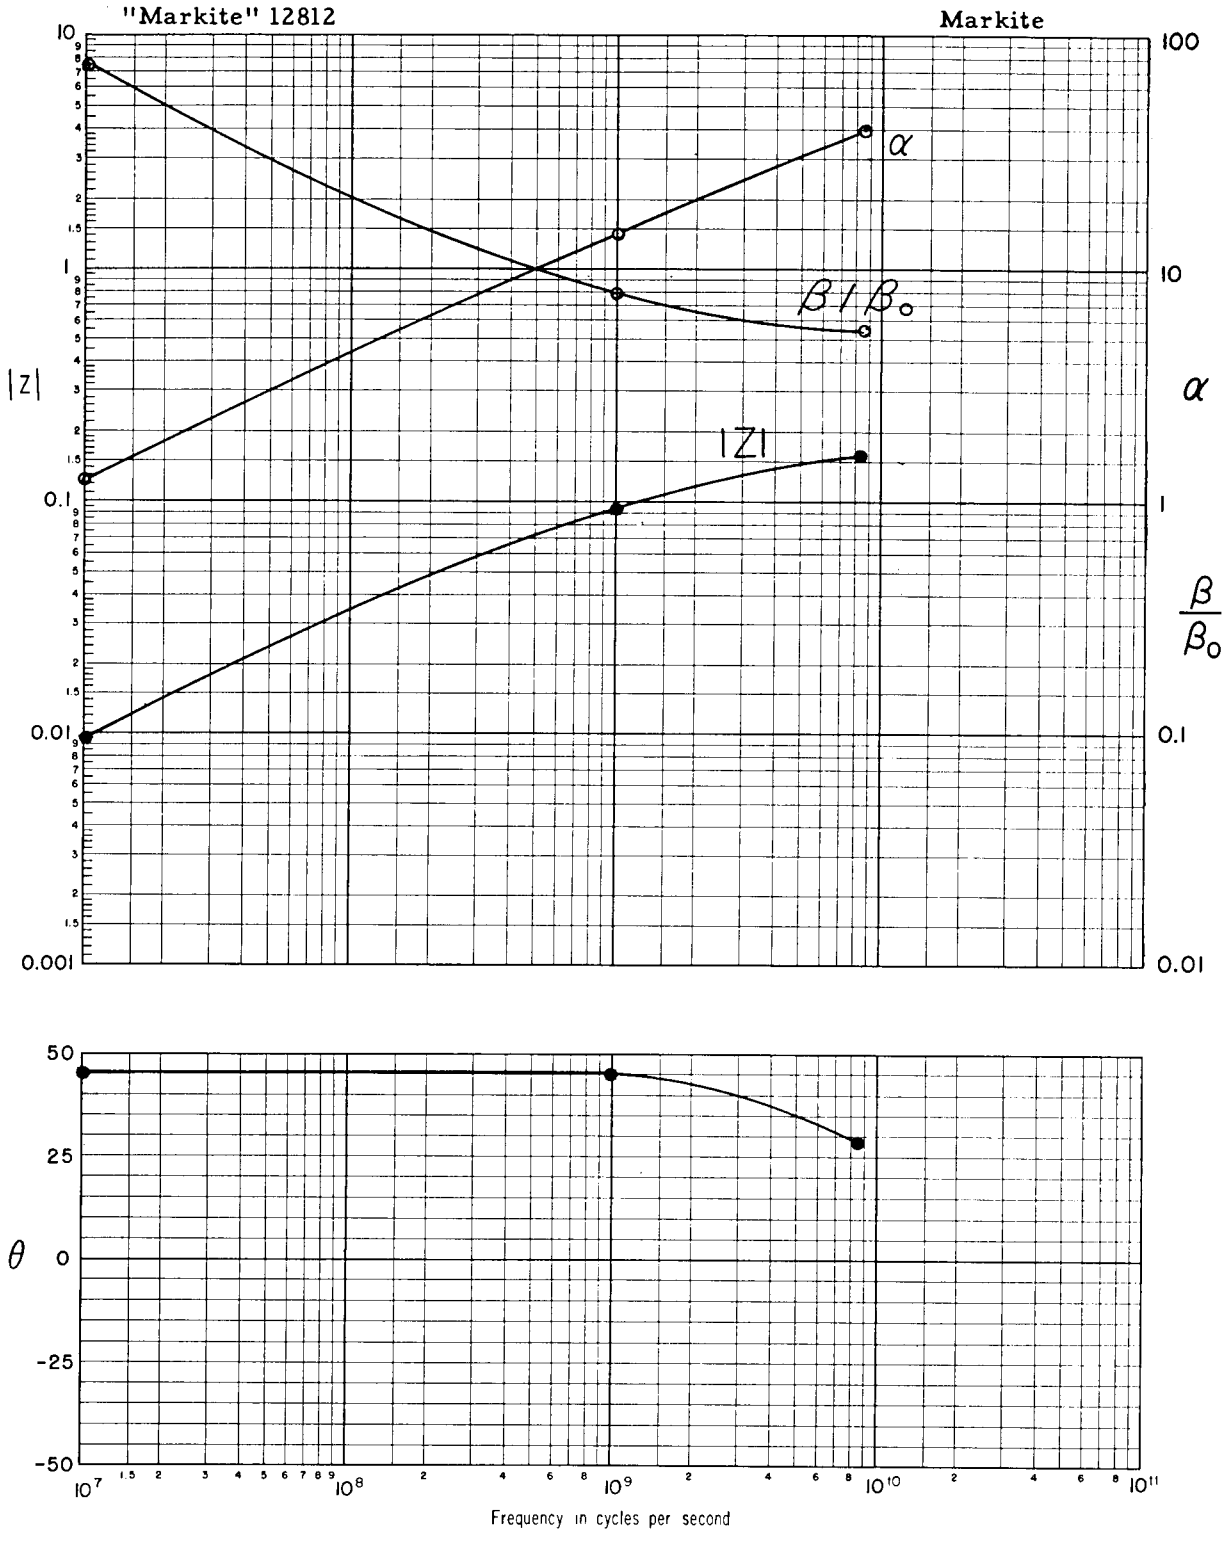


V D. Carbon-Plastic Mixtures

"Eccosorb" HF X122
(43.6% Graphite, 56.4% Polyester Resin) Emerson and Cuming

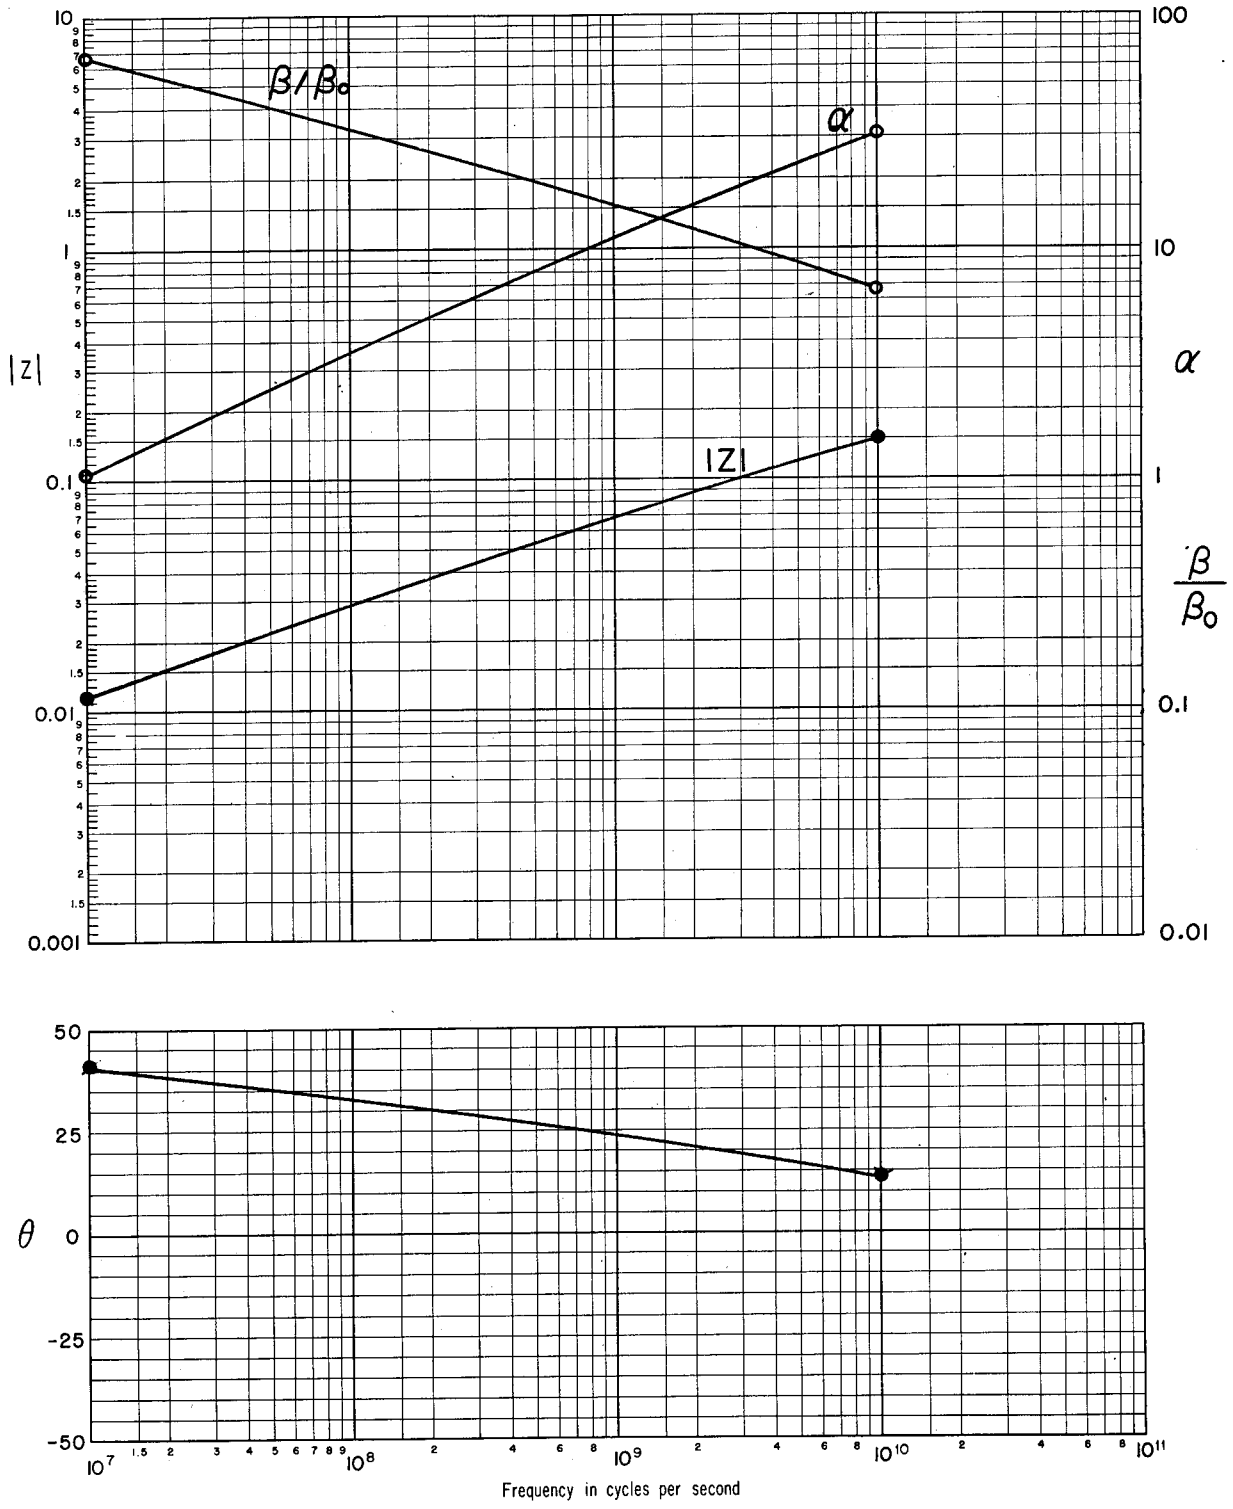


V D. Carbon-Plastic Mixtures

"Eccosorb" HF X123 Emerson and Cuming
(16.2% Acetylene Black, 83.8% Polyester Resin)

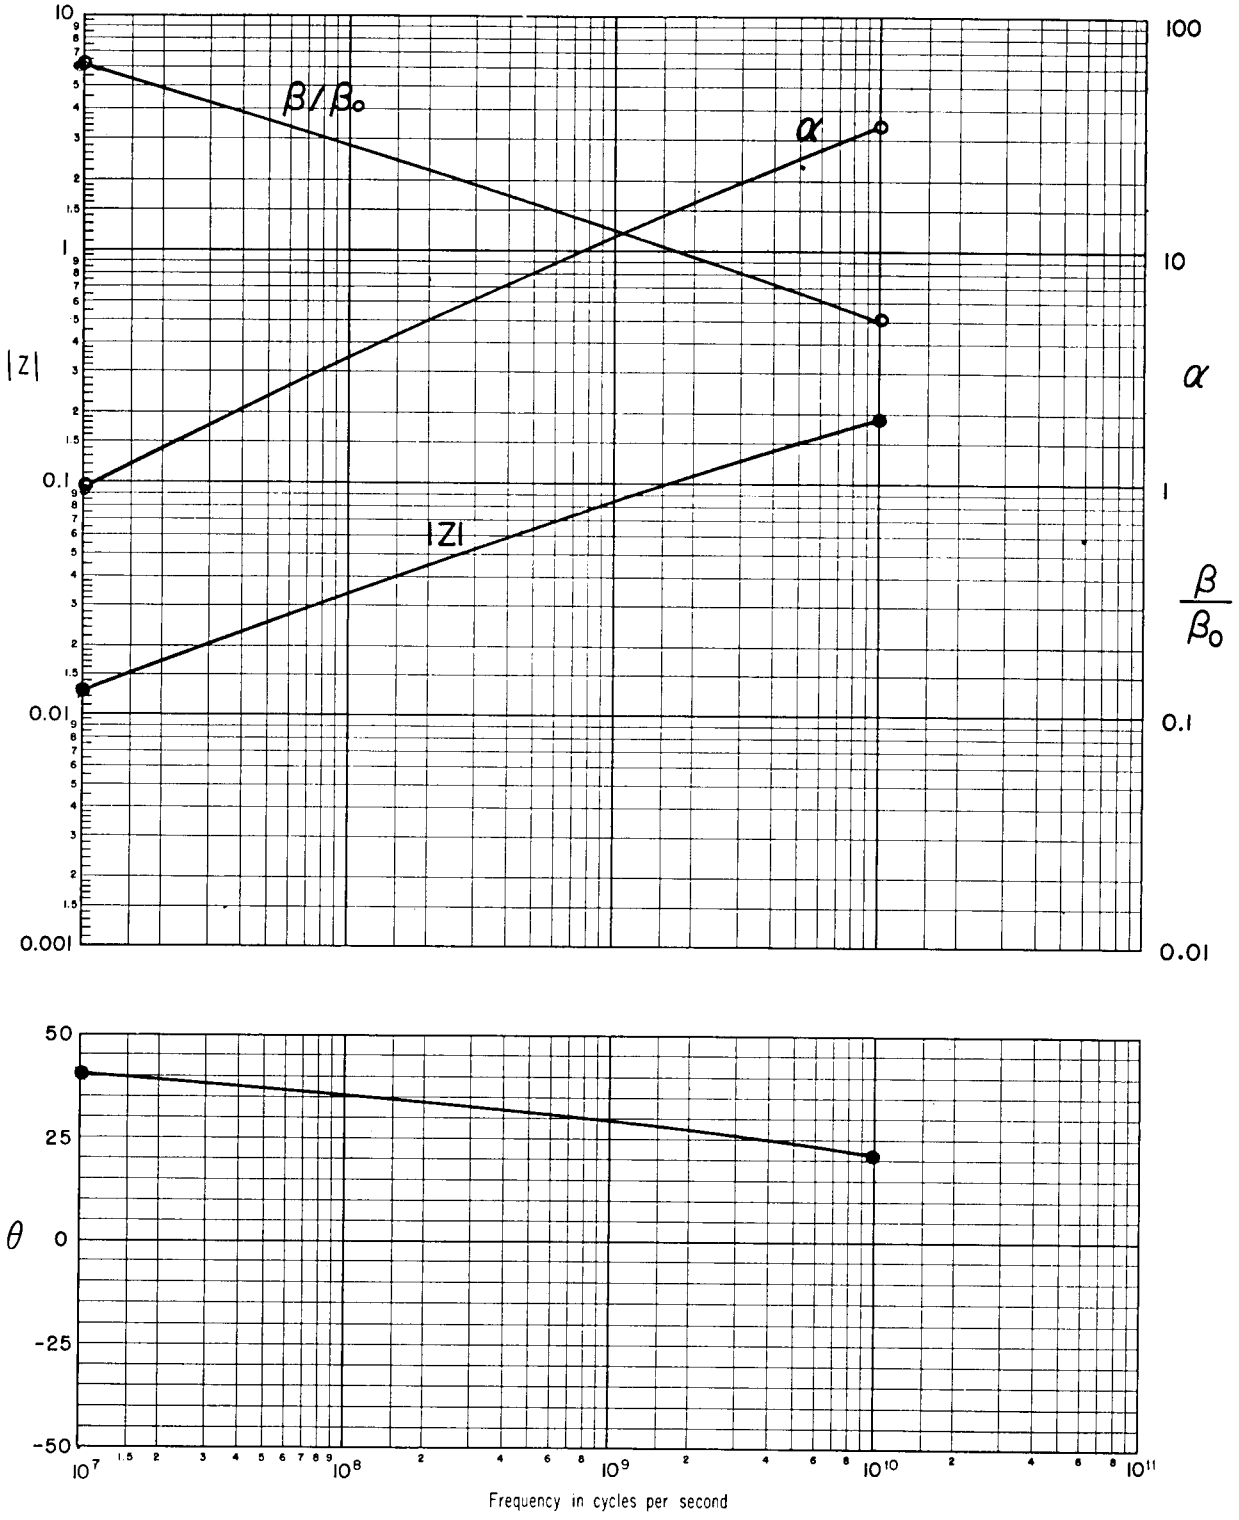

V D. Carbon-Plastic Mixtures


50% Polystyrene, 50% Carbon (Cabot's no. 9) Lab. Ins. Res.
molded at 1000 psi

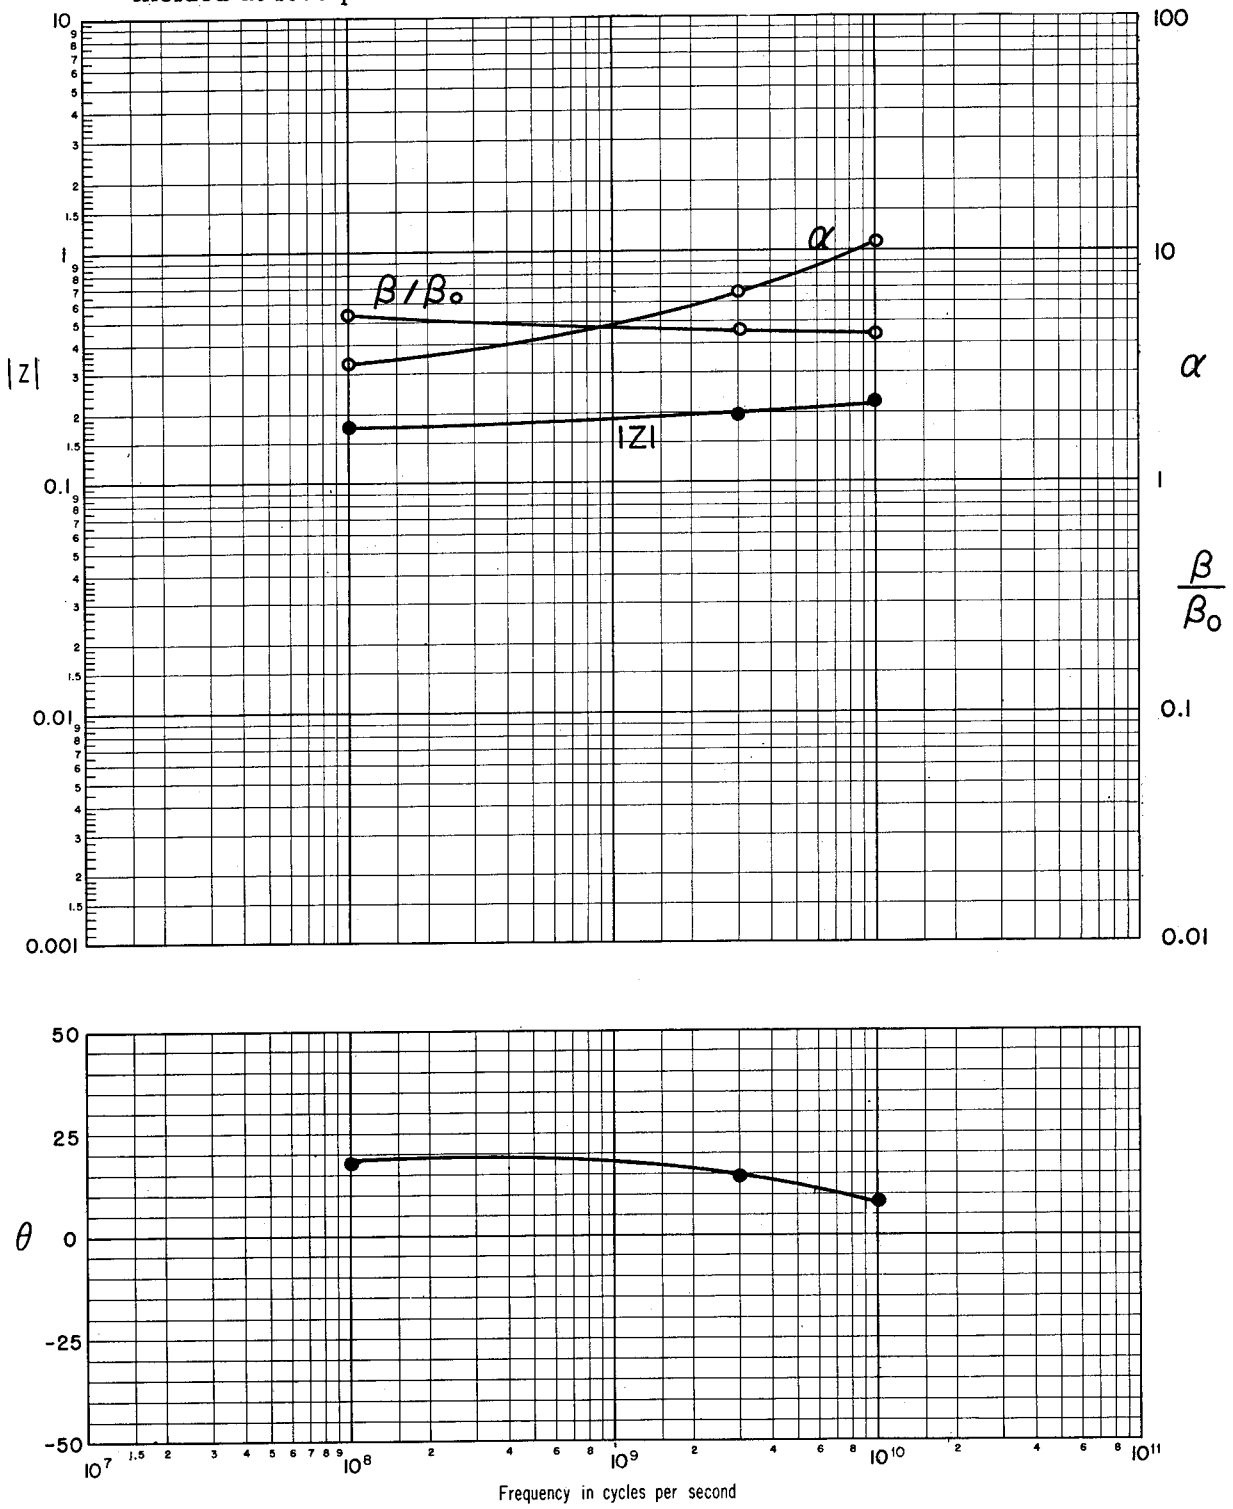

V D. Carbon-Plastic Mixtures

50% Polystyrene, 50% Carbon (Cabot's no. 9) molded at 10,000 psi


Lab. Ins. Res.

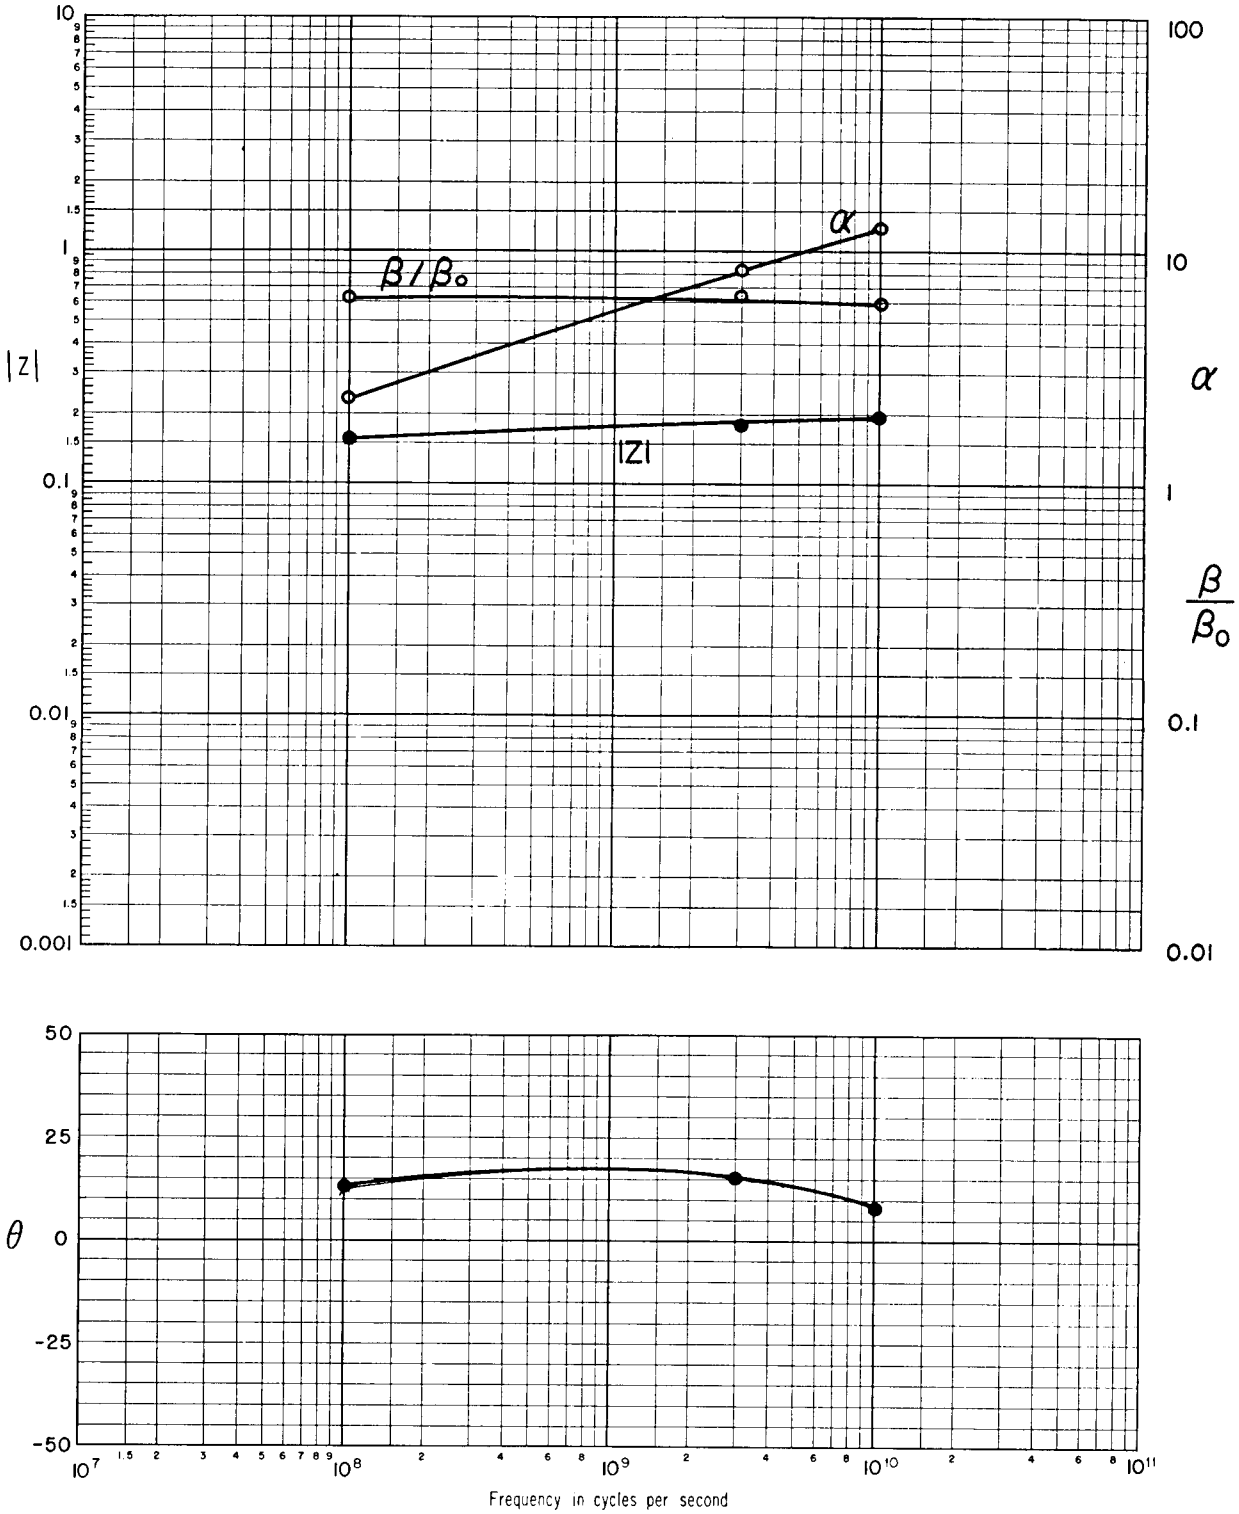


V D. Carbon-Plastic Mixtures

"Chemelac"M1414
(75%"Teflon," 25% Graphite)


U. S. Gasket

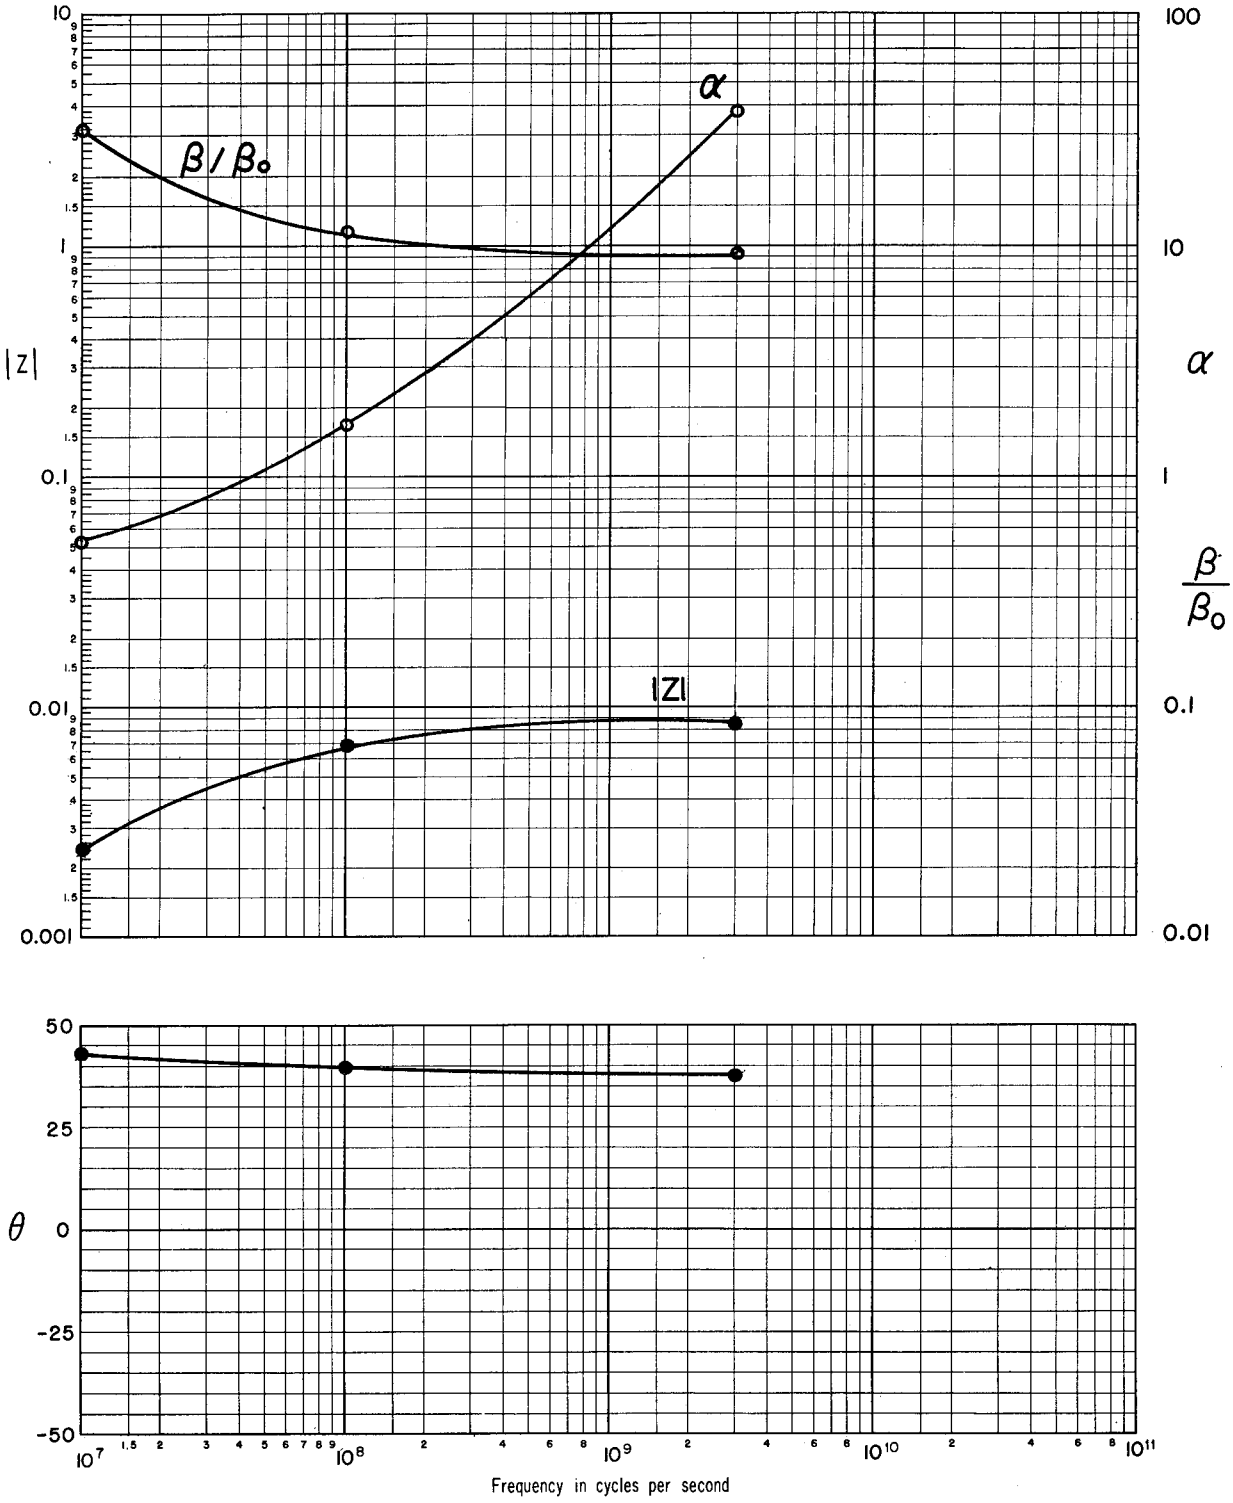

V E. Magnetic-Plastic Mixtures

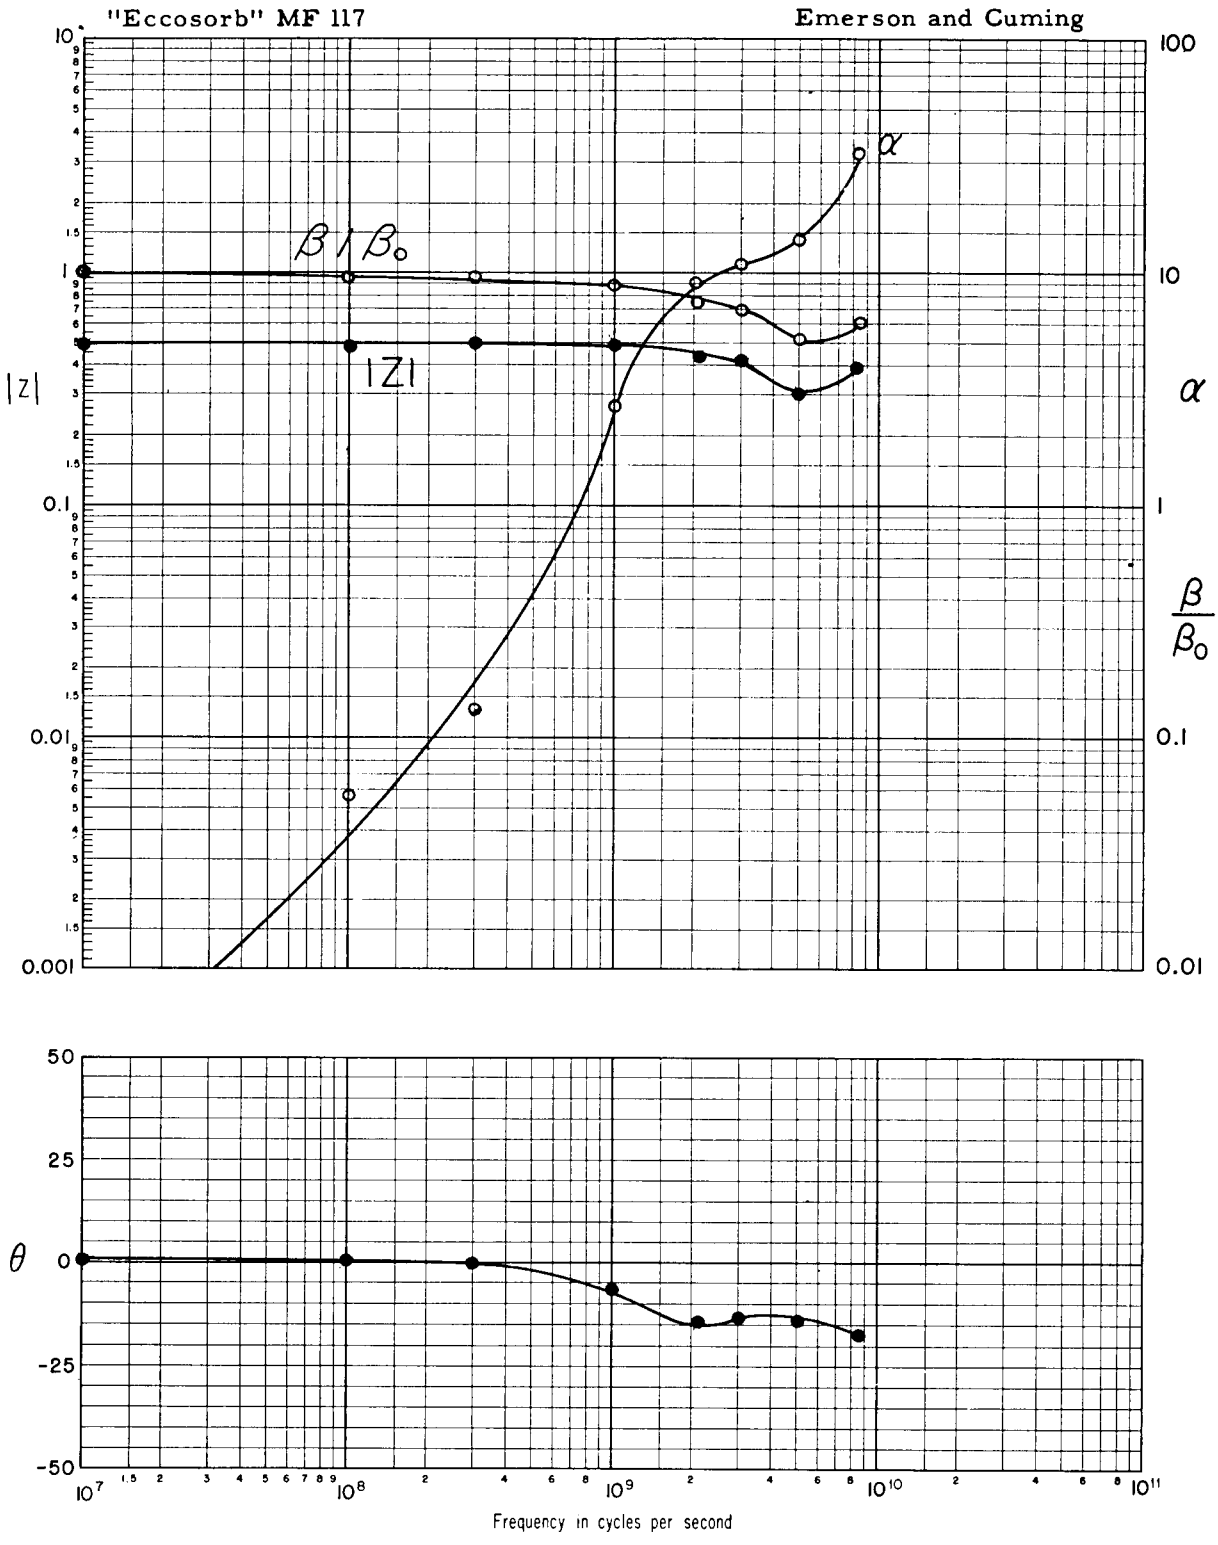


V E. Magnetic-Plastic Mixtures

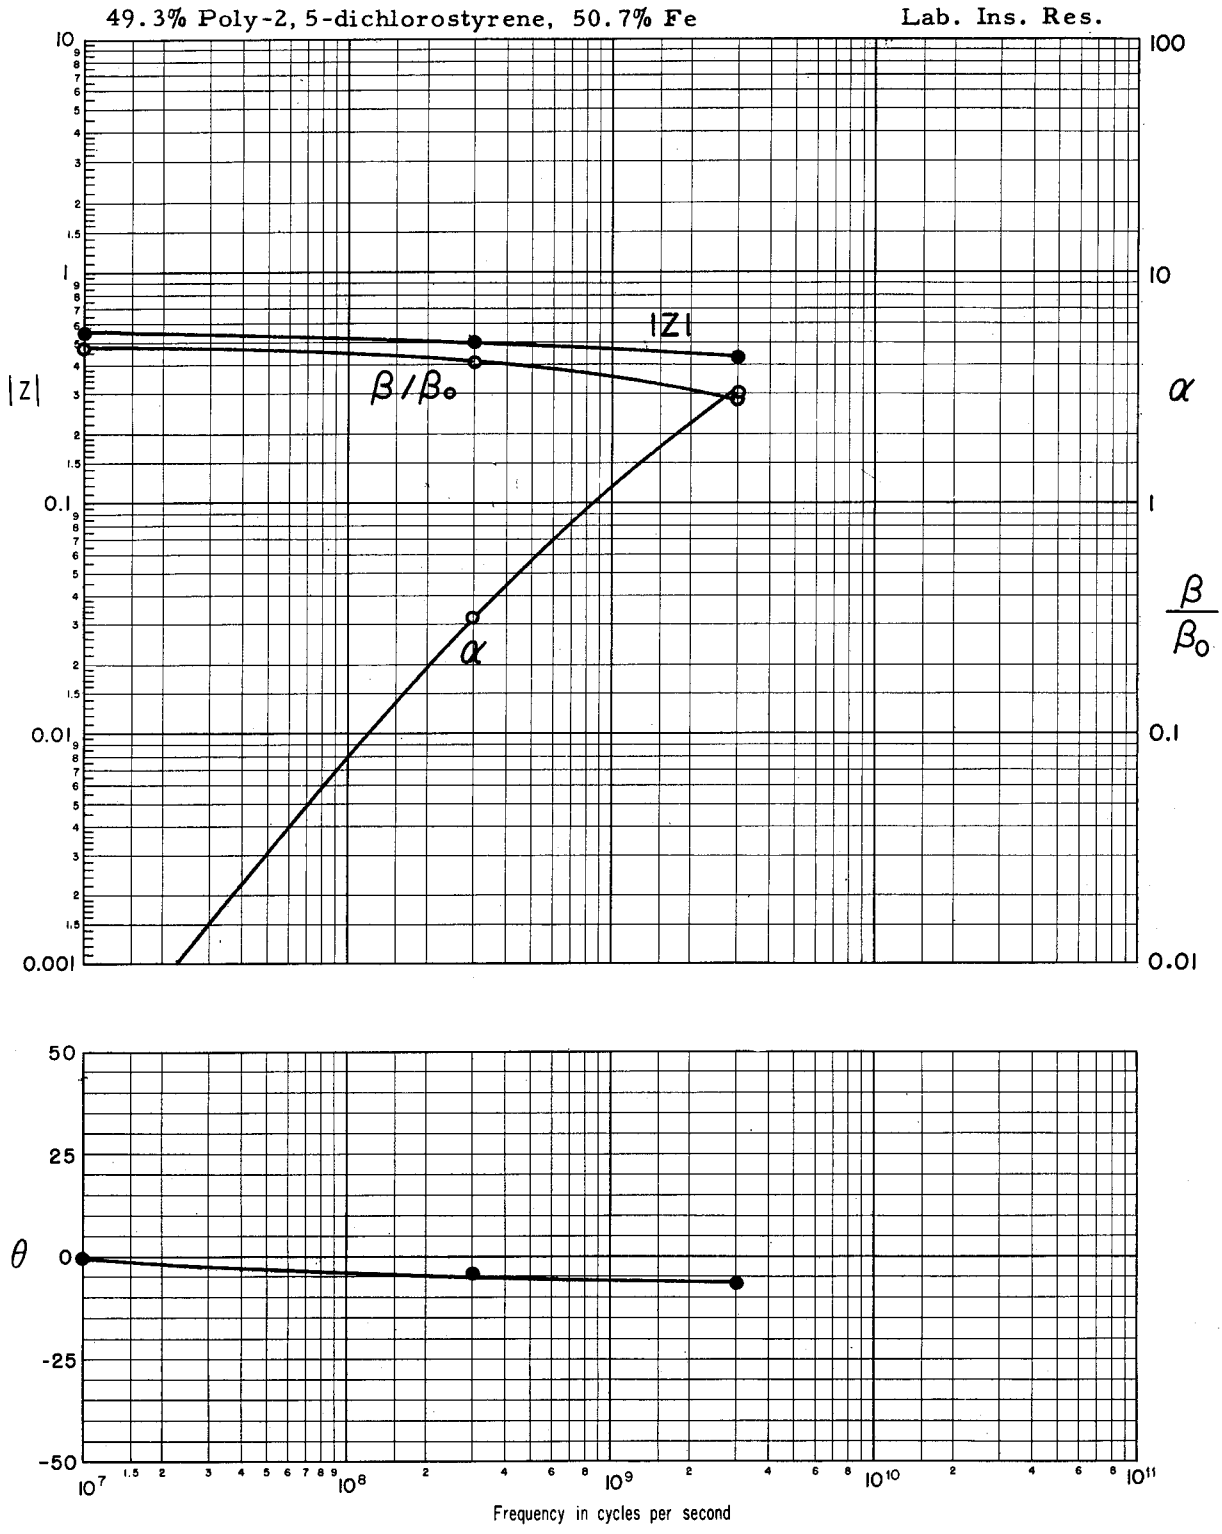

V E. Magnetic-Plastic Mixtures

"Ferrotron" Core Material, Type 119 Polymer Corp.

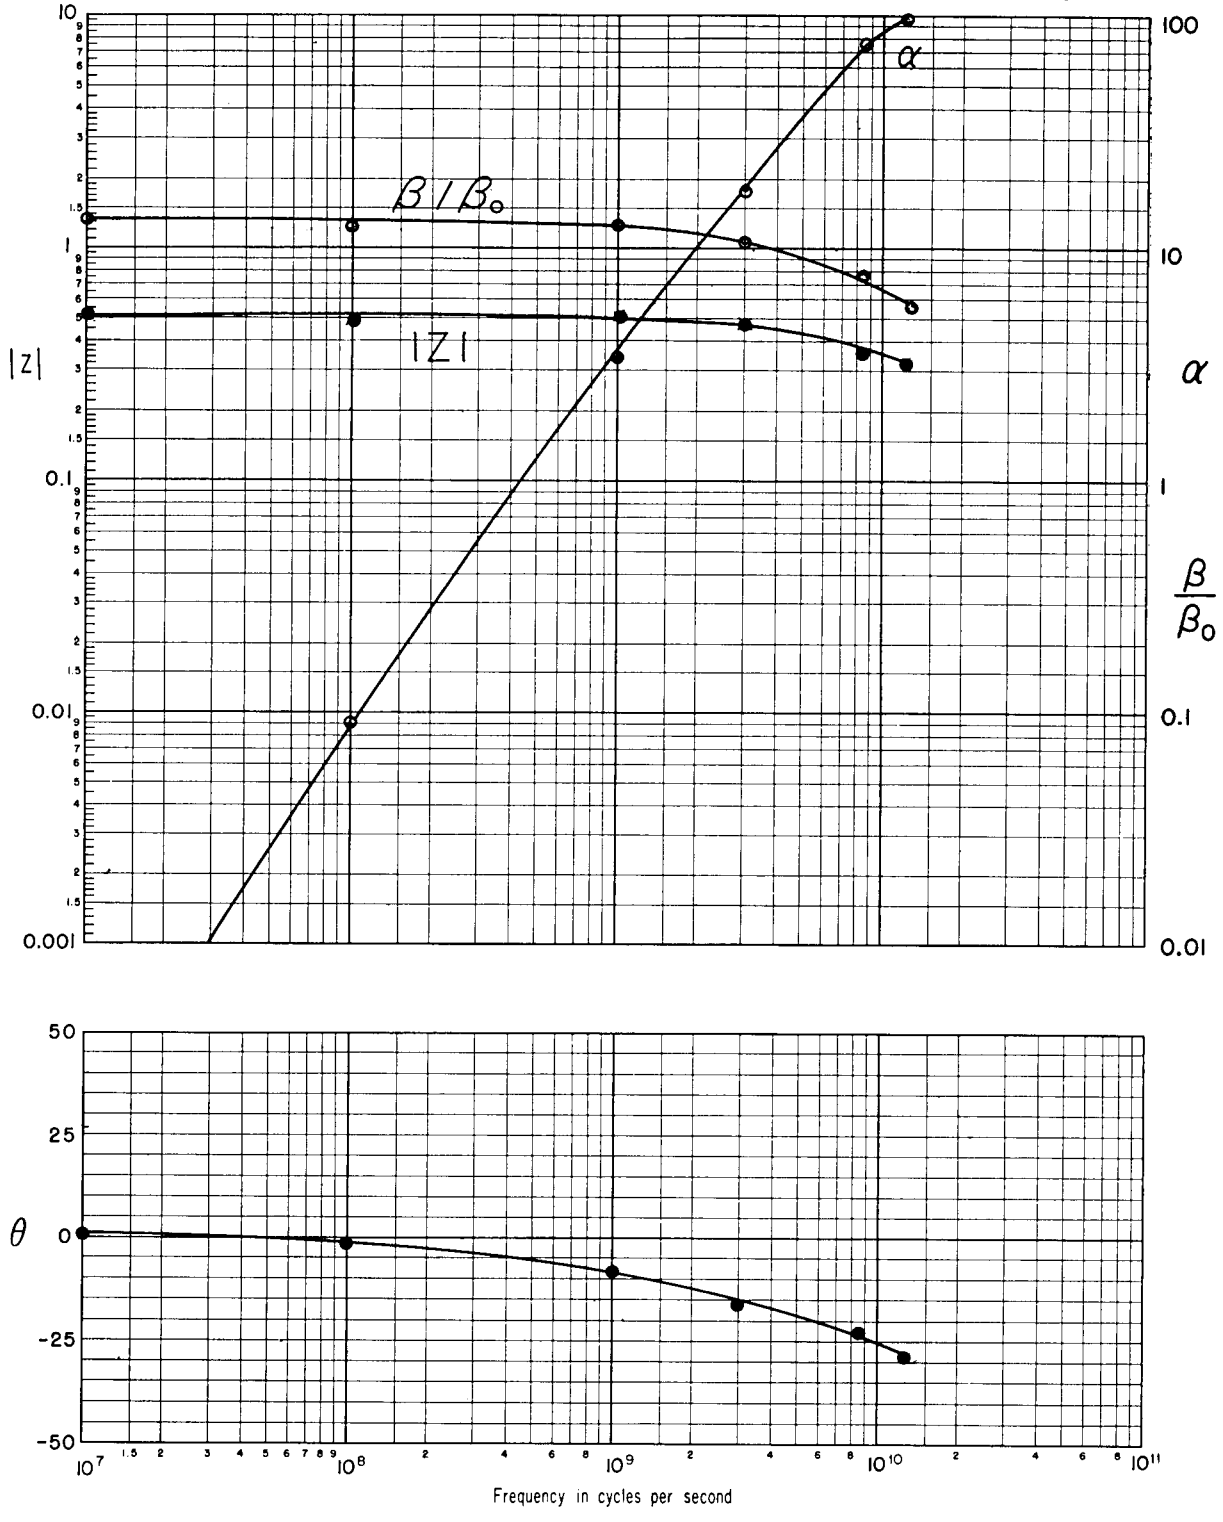

Company Index for Vols. IV* and V

Aircraft-Marine Products, Inc., IV-14; V-74
2102 Paxton St.
Harrisburg 2, Pa.

Air Reduction Sales Co., V-20
122 Mt. Vernon St.
Dorchester, Mass.

Allison, William M., and Co., Iv-58
162 Water St.
New York, N.Y.

Amber Mines, Inc., IV-55
353 Fifth Ave.
New York, N.Y.

American Cyanamid Co., IV-21-23, 38, 46, 112, 118-121; V-8, 106, 107
Plastics Devel. Labs.
1937 West Main St.
Stamford, Conn.

American Feldmuehle Corp., V-21, 30
11 West 42nd St.
New York 36, N.Y.

American Lava Corp., IV-3, 4, 6, 78-82, 88-93, 100; V-1, 2, 4, 5, 21, 31-39, 58-61, 75, 234
219 Kruesi Bldg.
Chattanooga 5, Tenn.

American Optical Co., IV-9
2 Mechanic St.
Southbridge, Mass.

American Phenolic Corp., IV-28
1830 South 54th Ave.
Chicago 50, Ill.

American Smelting and Refining Co., IV-13
120 Broadway
New York 5, N.Y.

Atlas Powder Co., V-11, 12
New Murphy Road
Wilmington 99, Del.

Bakelite Corp., IV-15, 16, 20, 27-29, 36, 48, 57, 58, 64; V-12
30 East 42nd St.
New York 17, N.Y.

Bell Telephone Laboratories, IV-3, 83; V-56, 57
463 West St.
New York, N.Y.

Beryllium Corp., The, V-21, 52, 53
Tuckerton Rd.
Reading, Pa.

Bromund, E.A., and Co., IV-57
11-A Warren St.
New York, N.Y.

Brush Electronics Co., IV-1, 73
3405 Perkins Ave.
Cleveland 14, O.

California Research Corp., IV-65
Box 1627
Richmond, Calif.

Candy and Co., Inc., IV-57
35th St. at Maplewood Ave.
Chicago, Ill.

Cantol Wax Co., IV-59
211 N. Washington St.
Bloomington, Ind.

Carborundum Co., The, V-6, 76-79
Niagara Falls, N.Y.

Catalin Corp. of America, IV-16-18, 36, 39, 119
Plant and Labs.
Fords, N.J.

Celanese Corp. of America, IV-24, 25, 114, 115; V-9, 10, 12, 90
Plastics Div.
290 Ferry St.
Newark 5, N.J.

---

* Add 301 to Vol. IV page numbers to find corresponding page in "Dielectric Materials and Applications," A.R. von Hippel, Editor, The Technology Press, Mass. Inst. Tech., and John Wiley and Sons, New York, 1954.

Company Index (cont.)

Cellular Rubber Products, Inc., IV-51
1000 Norwich Rd.
Willimantic, Conn.

Central Scientific Co., IV-56
79 Amherst St.
Cambridge, Mass.

Centralab Div., Globe-Union, Inc., IV-3, 84-87
932 E. Keefe Ave.
Milwaukee 1, Wis.

Ciba Co., Inc., IV-21, 49, 50, 125
Plastics Div.
627 Greenwich St.
New York, N.Y.

Components and Systems Lab.
See: U.S., Components and Systems Lab.

Continental-Diamond Fibre Co., IV-18, 19, 21, 26, 27, 31, 32; V-8, 12, 14, 80-83, 88, 93, 104, 108, 114
Bridgeport, Pa.

Coors Porcelain Co., IV-6, 94-99; V-2, 21, 40
Ford St.
Golden, Colo.

Cornell Aeronautical Labs., IV-48, 124
Cornell University
Ithaca, N.Y.

Corning Glass Works, IV-9-11, 26, 41, 42, 102, 103; V-2, 5, 6, 41, 62-71
Physical Lab.
Res. and Devel. Dept.
Corning, N.Y.

Crowley, Henry I., and Co., Inc., IV-4, 7; V-217-219
1 Central Ave.
West Orange, N.J.

Delaware Research and Development Corp., V-9
222 Sunset Drive, Delaire
Wilmington 3, Delaware

Dennison Mfg. Co., IV-58
45 Ford Ave.
Framingham, Mass.

Dewey and Almy Chemical Co., IV-38
Organic Chemicals Div.
62 Whittemore Ave.
Cambridge 40, Mass.

Diamonite Products Div., V-2, 3, 42-45
U.S. Ceramic Tile Co.
217 4th St. N.E.
Canton 2, Ohio

Dow Chemical Co., IV-36-42, 46, 64, 117; V-91
Plastics Div.
1000 Main St.
Midland, Mich.

Dow Corning Corp., IV-26, 27, 41, 42, 54, 55, 66, 67, 126; V-9, 20, 94, 95
592 Saginaw Rd.
Midland, Mich.

Du Pont, E.I. de Nemours and Co.
Electrochemicals Dept., IV-33, 64
Du Pont Bldg.
Wilmington 98, Del.

Film Dept., V-9, 13, 92
Nemours Bldg.
Wilmington 98, Del.

Organic Chemicals Dept., IV-53
(Elastomers Div.)
Dept. RT
Wilmington 98, Del.

Photo Products Dept., V-13, 109
Wilmington 98, Del.

Pigments Dept., IV-4
Nemours Bldg.
Wilmington 98, Del.

Polychemicals Dept., IV-23, 25, 27, 32, 34, 35, 58, 113; V-10, 89
Wilmington 98, Del.

Textile Fibers Dept., V-8, 10, 12, 14, 110
Nemours Bldg.
Wilmington 98, Del

Company Index (cont.)

Durez Plastics, IV-17, 20
Div., Hooker Electro-chemical Co.
17 Walck Rd.
North Tonawanda, N.Y.

Durite Plastics, Inc.,* IV-17, 19
5000 Summerdale Ave.
Philadelphia, Pa.

East Coast Aeronautics, Inc., V-11
10 Pelham Parkway
Pelham Manor 65, N.Y.

Eastman Kodak Co., IV-15, 62
343 States St.
Rochester 4, N.Y.

Electronic Mechanics, Inc., IV-13, 108
70 Clifton Blvd.
Clifton, N.J.

Emerson and Cuming, V-7, 8, 10, 11, 13-15, 115, 237, 238, 242
869 Washington St.
Canton, Mass.

Engineering Research and Devel. Lab.
See: U.S., Eng. Res. and Devel. Lab.

Enjay Co., Inc., IV-28, 39, 50
15 West 51st St.
New York 19, N.Y.

Esso Laboratories
See: Enjay Co., Inc.

Ethylene Chemical Corp., V-10
245 Broad St.
Summit, N.J.

Ferroxcube Corp. of America, V-4
500 E. Bridge St.
Saugerties, N.Y.

Filtered Rosin Products, Inc., IV-56
Baxley, Ga.

Formica Co., The, IV-17, 20, 21, 25, 46, 47
4614 Spring Grove Ave.
Cincinnati 32, O.

Frenchtown Porcelain Co., IV-6; V-3, 48, 49
99 Muirhead Ave.
Trenton 9, N.J.

General Aniline and Film Corp., IV-34, 46
230 Park Ave.
New York, N.Y.

General Cable Corp., IV-52
Bayonne, N.J.

General Ceramics Co., IV-4, 8, 83; V-3, 4, 54, 55, 159-175, 191-204, 220-233
Keasbey, N.J.

General Electric Co.,
100 Woodlawn Ave., IV-63-65
Pittsfield, Mass.

Chemical Materials Dept., IV-48
1 Plastics Ave.
Pittsfield, Mass.

Plastics Dept., IV-50
1 Plastics Ave.
Pittsfield, Mass.

1 River Rd., IV-13, 106, 107
Schenectady, N.Y.

Silicone Products Dept., IV-55, 67; V-127-129
Waterford, N.Y.

Lamp Division, IV-11, 104; V-72, 73
Nela Park
Cleveland 12, O.

*Now The Borden Co., Chemical Div., Dept. T-56, 350 Madison Ave., New York 17, N.Y.

Company Index (cont.)

General Mills, Inc., IV-23
Central Ave. at 17th
Minneapolis 13, Minn.

Glastic Corp., The, IV-47, 49
Glenridge at Princeton
Cleveland 3, O.

Glenco Corp., IV-5, 6
200 Durham Ave.
Metuchen, N.J.

Glyco Products Co., IV-56, 59
Empire State Bldg.
New York, N.Y.

Goodrich, B.F., Chemical Co., IV-29, 30
Avon Lake Experimental Station
P.O. Box 122
Avon Lake, O.

Goodyear Aircraft Corp., IV-48; V-8, 9, 84-87, 96-101
1220 Massillon Rd.
Akron 15, O.

Goodyear Tire and Rubber Co.
Plastics Dept., IV-40, 51, 52
Akron 16, O.

Gulf Oil Corp., IV-58
2900 Gulf Bldg.
Pittsburgh, Pa.

Hardman, H.V., Co., Inc., IV-49, 51
571 Cortland St.
Belleville 9, N.J.

Harshaw Chemical Co., The, IV-1, 2; V-1, 30
1933 East 97th St.
Cleveland 6, O.

Hartwell, H.N., and Sons, Inc., V-10
31 St. James Ave.
Boston, Mass.

Haveg Corp., V-17
900 Greenbank Rd.
Wilmington 8, Del.

Hercules Powder Co., Inc., IV-23; V-16
Cellulose Products Dept.
Parlin, N.J.

Hood Rubber Co., IV-22
98 Nichols Ave.
Watertown 72, Mass.

Hooker Electrochemical Co., IV-62; V-13
1940 Ward St.
Niagara Falls, N.Y.

Plastics Div., see: Durez

Houghton Labs., Inc., IV-50; V-15, 16, 126
4151 Russell St.
Olean, N.Y.

Hunson, C.W., V-7
P.O. Box 244
Sioux Falls, S.D.

Irvington Varnish and Insulator Co., V-17
17 Argyle Terrace
Irvington 11, N.J.

Johns-Manville, IV-13
22 East 40th St.
New York 16, N.Y.

Kearfott Co., Inc., V-3, 46, 47
1378 Main Ave.
Clifton, N.J.

Kearney, James R., Corp., IV-52
4236 Clayton Ave.
St. Louis 10, Mo.

Kellog, M.W., Co., The, IV-31, 58, 63, 116; V-10, 18, 19, 102, 103, 130, 131
Foot of Danforth Ave.
Jersey City 3, N.J.

Knox Porcelain Corp., IV-6, 100
2700 Mynders St.
Knoxville 11, Tenn.

Company Index (cont.)

Kuhne-Libby Co., IV-57
54 Front St.
New York, 4, N.Y.

Laminated Plastics, Inc.
See: Glastic Corp.

Linde Air Products Co., The,
IV-1, 2, 72, 77; V-1, 26-28
East Park Dr. and Woodward Ave.
Tonawanda, N.Y.

Lovell Chemical Co., IV-57, 58; V-16
Watertown 72, Mass.

Lucoflex Plastic Fabricating, Inc., IV-30
242 Village St.
Medway, Mass.

Mallinckrodt Chemical Works,
IV-44, 45, 61, 62
Second and Mallinckrodt Sts.
St. Louis 7, Mo.

Marbon, Chemical Div. of Borg-Warner Corp., IV-38
1926 West 10th Ave.
Gary, Ind.

Marco Chemicals, Inc.*, IV-47
Sewaren, N.J.

Markite Co., V-22, 235, 236
155 Waverly Place
New York 14, N.Y.

Mass. Inst. of Technology

Cryogenic Eng. Lab., V-18
Rm 41-202
77 Mass. Ave.
Cambridge 39, Mass.

Lab. for Insulation Research,
IV-1, 2, 5, 11, 12, 26, 37, 41-46, 62, 64, 105; V-1, 133-139, 142-158, 177-180, 183-190, 206-216, 239, 240, 243
Rm 4-244, 77 Mass. Ave.
Cambridge 39, Mass.

Lincoln Laboratory, V-140, 141, 176, 181, 182
Rm 20C-105
77 Mass. Ave.
Cambridge 39, Mass.

Mathieson Chemical Corp.,
See: Olin Mathieson

Mica Insulator Co., IV-21
801 Broadway
Schenectady, N.Y.

Minnesota Mining and Mfg. Co.,
IV-63; V-16, 17, 22
900 Fauquier Ave.
St. Paul 6, Minn.

Mitchell-Rand Insulation Co., Inc.,
IV-57-59
51 Murray St.
New York, N.Y.

Monsanto Chemical Co.
Plastics Division, IV-15, 18, 20, 22, 24, 30, 36, 37, 41-45, 63, 64
100 Monsanto Ave.
Springfield 2, Mass.

Rubber Chemical Sales, Dept. of
Organic Chemicals Div., V-11
920 Brown St.
Akron 11, Ohio

Organic Chemicals Div., V-19
800 N. 12th Blvd.
St. Louis 1, Mo.

Morse, Herbert B., and Co., V-16, 17
354 Washington St.
Wellesley, Mass.

Mycalex Corp. of America, IV-13; V-7, 79
Dept. 120-A, P.O. Box 311
Clifton, N.J.

Narmco Resins and Coatings Co., V-8
Victoria and Placentia
Costa Mesa, Calif.

National Research Corp., V-3
70 Memorial Drive
Cambridge, Mass.

* Now Celanese Corp. of America, 290 Ferry Street, Newark 5, N.J.

Company Index (cont.)

Naugatuck Chemical, Div. of
U.S. Rubber Co., IV-47, 53
132 Elm St.
Naugatuck, Conn.

Norton Co., IV-1, 6; V-3, 29, 49
50 New Bond St.
Worcester 6, Mass.

Olin Mathieson Chemical Corp.,
IV-41; V-20
Mathieson Bldg.
Baltimore 3, Md.

Owens-Corning Fiberglas Corp.,
IV-11, 16, 22, 47, 48; V-6, 8, 13
Research and Development
Labs.
Newark, O.

Pennsylvania Industrial
Chemical Corp., IV-39, 50
Clairton, Pa.
(Products distributed by
Standard Chemical Co.,
Akron 8, O.)

Phillips Petroleum Co., V-19
Chemical Products Dept.
Bartlesville, Okla.

Phillips Chemical Co., V-10
Plastics Sales Div.
Bartlesville, Okla.

Pittsburgh Corning Corp., IV-11;
V-13, 19
Dept. TR, One Gateway Center
Pittsburgh 22, Pa.

Plaskon Div., IV-22, 23, 47, 49, 123;
V-112, 113
Allied Chemical and Dye Corp.,
Dept. R-2
Toledo, O.

Plastic Metals, Div. of National
U.S. Radiator Corp., IV-43, 44
123 Bridge St.
Johnstown, Pa.

Plax Corp., IV-35
P.O. Box 1019
Hartford 1, Conn.

Polaroid Corp., IV-35, 37, 40; V-11
741 Main St.
Cambridge, Mass.

Polymer Corp. of Pennsylvania,
V-17, 18, 205, 244
2140 Fairmount Ave.
Reading, Pa.

Procter and Gamble Co., IV-60
Ivorydale
Cincinnati 1, O.

Raybestos-Manhattan, Inc., V-8, 9
Asbestos Textile and Packing Div.
Manheim, Pa.

Raytheon Mfg. Co., V-3
90 Willow St.
Waltham, Mass.

Resinous Products Div.
See: ROHM and HAAS Co.

Rex Corp., IV-40; V-11, 105
Hayward Rd.
West Acton, Mass.

Rezolin, Inc., IV-19
5736 West 96th St.
Los Angeles 45, Calif.

Robertson, H.H., Co., IV-48, 123;
V-12, 19
2400 Farmers Bank Bldg.
Pittsburgh 22, Pa.

Rogers Paper Mfg. Co., IV-60
Manchester, Conn.

Rohm and Haas Co., IV-30, 34, 48,
62, 122; V-12, 111
712 Locust St.
Philadelphia 5, Pa.

Rubber Reserve Corp., IV-51, 52
Washington 1, D.C.

Rutgers University
School of Ceramics, V-4
New Brunswick, N.J.

Company Index (cont.)

St. Regis Paper Co., IV-17, 22
Panelyte Div.
Enterprise Ave.
Trenton, N.J.

Sauereisen Cements Co., V-7
3389 Sharpsbury Station
Pittsburgh 15, Pa.

Sharples Chemicals, Div., Penna.
Salt Mfg. Co., IV-63
Widner Bldg.
Philadelphia 9, Pa.

Shawinigan Products Corp., IV-34
Empire State Bldg.
New York 1, N.Y.

Shell Chemical Corp., IV-50;
V-16, 116-125
Resins and Plastics Dept.
50 West 50th St.
New York 20, N.Y.

Shell Devel. Co., IV-46-48
4560 Horton St.
Emeryville 8, Calif.

Shell Oil Co., IV-56, 66
Special Products Dept.
50 West 50th St.
New York 20, N.Y.

Socony Mobil Oil Co., Inc.,
IV-57, 58
Formerly Socony-Vacuum
Oil Co,, Inc.
26 Broadway
New York, N.Y.

Southern Alkali Corp., IV-48
Barberton, O.

Sperry Gyroscope Co., V-18
Lake Success
Great Neck, N.Y.

Sponge Rubber Products Co.,
IV-19, 31, 52
Shelton, Conn.

Sprague Electric Co., IV-39
149 Marshall St.
North Adams, Mass.

Spruce Pine Mica Co., V-7
Greene Bldg.
Spruce Pine, N.C.

Stanco Distributors, Inc., IV-65, 66
Chemical Products Dept.
See: Enjay Co., Inc.

Standard Oil Co. of N.J., IV-58
15 W 51st St.
New York, N.Y.

Standard Oil Devel. Co.
See: Enjay Co., Inc.

Sterling Varnish Co., The, V-18
1954 Ohio River Blvd.
Haysville Boro.
Sewickley P.O., Pa.

Stupakoff Ceramic and Mfg. Co.,
IV-6, 101; V-3, 4, 50, 51
Division of the Carborundum Co.
Hillview Ave.
Latrobe, Pa.

Syncor Products Co., V-6
22 Eastern Ave.
Malden, Mass.

Taylor Fibre Co., IV-18, 27, 111
Norristown, Pa.

Tennessee Eastman Corp., IV-24
Kingsport, Tenn.

Tennessee Marble, Inc., IV-13
Knoxville, Tenn.

Thiokol Chemical Corp., IV-54
780 North Clinton Ave.
Trenton 7, N.J.

Titanium Alloy Mfg. Div., IV-4, 5,
42, 43
National Lead Co.
Hyde Park Blvd.
Niagara Falls, N.Y.

Union Carbide and Carbon Corp.,
V-18
Silicones Div., Dept. EE
30 E. 42nd St.
New York 17, N.Y.

U.S. Ceramic Tile
See: Diamonite Products Div.

Company Index (cont.)

U.S. Gasket Co., IV-32, 33;
608 North 10th St.
Camden, N.J.

United States (Government)

Components and Systems Lab., IV-9, 101
Air Materiel Command
Wright-Patterson Air Force Base
Dayton, O.

Engineering Research and Devel. Lab., IV-2, 74-76
Fort Belvoir, Va.

National Bureau of Standards, IV-40
Washington, D.C.

War Department, IV-15
Picatinny Arsenal
Dover, N.J.

U.S. Industrial Chemicals Co., IV-62
99 Park Ave.
New York 16, N.Y.

U.S. Polymeric Chemicals, Inc., V-9
Canal and Ludlum Sts.
Stamford, Conn.

U.S. Rubber Co., IV-31, 40, 52, 53, 56
General Labs.
Passaic, N.J.

U.S. Stoneware Co., The, V-21, 51
5300 East Talmadge Ave.
Akron, O.

Victor Chemical Works, IV-48
155 North Wacker Drive
Chicago 6, Ill.

War Dept., Picatinny Arsenal
See: U.S. War Dept.
Picatinny Arsenal

Weber, Hermann, and Co., IV-51
76 Beaver St.
New York 5, N.Y.

Western Gold and Platinum Works, V-4, 52
Belmont, Calif.

Westinghouse Electric Corp., Research Labs., IV-18, 19, 22
East Pittsburgh, Pa.

Zinsser, Wm., and Co., IV-55, 56
513 West 58th St.
New York 11, N.Y.

Zophar Mills, Inc., IV-59
112-130 26th St.
Brooklyn 32, N.Y.

Materials Index for Volumes IV* and V

"Acrawax" C, IV-56

Acrylate resins, IV-34, 35; V-10

Acrylonitrile-butadiene copolymer, IV-53

AFC Alumina, V-21

Air seal, IV-52

"Alathon," IV-27, 70

Alcohols, IV-62

"Alite" AP-212 and AP-216, V-21

"Alite" Ap-312, V-21, 51

Alkyd resins, IV-47-49, 123, 124; V-112, 113

Allyl resins, IV-47, 48

Allymer CR-39, CR-39 + glass, IV-48

"AlSiMag" A-35, IV-3, 80

"AlSiMag" A-196, IV-3, 78, 79

"AlSiMag" 211, IV-3

"AlSiMag" 288, IV-3, 81

"AlSiMag" 243, IV-3, 82

"AlSiMag" 393, IV-3

"AlSiMag" 475, V-5, 59-61

"AlSiMag" 491, IV-6, 100

"AlSiMag" 491 (blue), V-1, 32, 33

"AlSiMag" 505, IV-82

"AlSiMag" 513 (pink), V-1, 34, 35

"AlSiMag" 544, V-21, 31

"AlSiMag" 548, V-21, 31

"AlSiMag" 576, V-2, 36, 37

"AlSiMag" 577, V-4, 58

"AlSiMag" 602, V-21, 75

"AlSiMag" 614, V-2

"AlSiMag" 652, V-21, 38, 39

"AlSiMag" 5050, V-234

Aluminas, IV-6, 96-99; V-1, 2, 3, 4, 21, 23, 3-52

Alumina Mullite, V-3

Aluminum oxide, IV-3, 6, 72, 96-100; V-1, 2, 3, 4, 26, 27, 28

Aluminum silicate, V-6

"Alvar" 11/90, IV-34

Amber, IV-55

Amer. Cyanamid 405 resin, V-8

Amer. Cyanamid, see "Laminac," "Melmac," "Beetle"

Ammonium dihydrogen phosphate, IV-1

"Amplifilm," IV-14; V-74

Aniline-formaldehyde resins, IV-21

"Apiezon" Wax "W", IV-56

"Araldite" Adhesive, Type I, IV-50 (natural and silver)

"Araldite" Casting Resin, Type B, IV-49, 125

"Araldite" Casting Resin G, IV-49

"Araldite" E-134, IV-49

"Aroclor" 1221, 1232, 1242, 1248, 1254, IV-63

"Aroclor" 1260, 1262, 5442, IV-64

"Aroclor" 1268, 4465, 5460, IV-15

Asbestos, IV-13

Asbestos filled plastics, IV-16; V-8, 9, 84, 85, 96, 97

Asphalts and Cements, IV-56

"Atlac" 382, V-11, 12

---

* Add 301 to Volume IV page numbers to find corresponding page in "Dielectric Materials and Applications," A.R. von Hippel, Editor, The Technology Press, Mass. Inst. Tech., and John Wiley and Sons, New York, 1954.

Materials Index (cont.)

"Bakelite" BM-120, IV-15, 16, 69

"Bakelite" BM-250, BT-48-306, BM-16981, and BM-16981 powder, IV-16

"Bakelite" BM-262, BM-1895, IV-20, 69

"Bakelite" BRS-16631 + glass, IV-48

"Bakelite" BV-17085 + glass, IV-16

"Bakelite" PLLA-5005, V-12

"Bakelite" polystyrenes, IV-36

"Bakelite" polyvinyl chloride-acetate , see "Vinylites"

Balata, precipitated, IV-51

Barium-strontium titanate, IV-5, 6

Barium titanate, IV-5; V-1

Barium titanate and plastic mixtures, IV-43

"Bayol," "Bayol"-16, IV-66

"Bayol"-D, "Bayol"-F, IV-65

Beeswax, white, yellow, IV-57

"Beetle" resin, IV-23

Bell Labs. F-66, IV-3, 83; V-56, 57

Bentonite, IV-14; V-74

Benzenes and diphenyls, chlorinated, IV-63

Benzenes, chloro-, IV-64

Benzoguanamine-formaldehyde resin, IV-23

Beryllium oxide, IV-6; V-21, 24, 52, 53

Biphenyls, chlorinated, IV-15, 63, 64

Biphenyl, diisopropyl and monoisopropyl, V-19

Bitumen, natural, IV-56

"Boltaron" 6200-10, V-10

Boron nitride, V-6, 76, 77

Boron nitride alloy, V-6, 79

Buna S (GR-S) and compounds, IV-52

Bureau of Standards Casting Resin IV-40

Butadiene-acrylonitrile copolymer, IV-53

Butadiene, chloro- , IV-53, 62

Butadiene-styrene copolymer, IV-38, 52

"Butvar," Low OH and 55/98, IV-34

n-Butyl alcohol, IV-62

Butyl rubbers, IV-52

Butyraldehyde, IV-62

Cable Oil 5314 and PL101270, IV-65

Calcium fluoride, V-1, 10

Calcium titanate, IV-5

Carbon, diamond, V-1

Carbon and plastic mixtures, IV-32, 41; V-239, 240

Carbon tetrachloride, IV-62

Carbonyl iron and plastic mixtures, V-15

"Catalin" 200, 500, and 700 base, IV-16, 17

"Catalin" 8012, IV-39, 119

"Catalin" EK 2784, IV-39

Celanese MR-31C, MR-33C, MX-186 and MX-218, V-12

Cellulose Acetate LL-1, IV-23

Cellulose acetate + plasticizer, IV-24

Cellulose acetates, IV-23, 24, V-9

Cellulose derivatives, IV-23-25; V-9, 90, 91, 92

Materials Index (cont.)

Cellulose nitrate and camphor, IV-25

Cellulose propionate, IV-25, 114; V 9, 90

Cellulose triacetate ("CTA"), V-9, 92

Cements and asphalts, IV-56

Cenco "Sealstix," IV-56

"Ceram" 61-1, V-5, 65

"Ceram" 61-2, V-5, 66

"Ceram" 61-3, V-5, 67

"Ceram" 61-4, V-6, 68

"Ceram" 61-5, V-6, 69

Ceramic NPOT 96, IV-4, 88, 89

Ceramic N750T96, IV-4, 90, 91

Ceramic N1400T110, IV-4, 92, 93

Ceramic T106, IV-4

Ceramics, IV-3, 78; V-30, 136, 206

Cerese Wax AA and brown, IV-57

Ceresin, white and yellow, IV-57

Cesium bromide, V-1

Cesium iodide, V-1

Cetylacetamide, IV-56

"Chemelac" M1405, M1406, M1407, M1411, and M1412, IV-32

"Chemelac" M1414, IV-32, V-241

"Chemelac" M1418-2, M1418-5, M1422, and M1423, IV-33

"Chemelac" B-3, IV-56

Chlorinated benzenes and biphenyls, IV-15, 63, 64

β-chloroethyl-2, 5-dichloro-benzene, IV-64

Chlorostyrenes, ortho and para, copolymer, IV-42

Chlorotrifluoroethylene dimer, trimer, V-18

Chlorotrifluoroethylene tetramer, pentamer, hexamer, V-19

"Cibanite," IV-21

Cobalt ferrite (M.I.T. samples), V-136, 177, 206

"Conolon" 506, V-8

Coors AB-2, IV-6, 98, 99

Coors AI-200, IV-6, 96, 97; V-2, 21, 40

Coors AL-100, V-2, 40

"Copolene" B, IV-28

"Corfoam" 114, IV-19

Corning aluminas, JB-123 and WD-131, V-2

Corning aluminas JD-40, JD-82, JB-183, V-2, 41

Corning Glass Nos. 0010, 0014, 0080, 0090, 0100, 0120, 1770, IV-9

Corning Glass No. 1990, IV-9, 102

Corning Glass Nos. 1991, 3320, 7040, 7050, IV-9

Corning Glass Nos. 7052, 7055, 7060, IV-10

Corning Glass No. 7070, IV-10, 102, V-62, 63

Corning Glass Nos. 7230, 7570, 7720, 7740, 7750, IV-10

Corning Glass No. 7900, IV-10, V-67

Corning Glass No. 7910, V-5

Corning Glass No. 7911, IV-10, 103

Corning Glass Nos. 8460, 8830, IV-10

Corning Glass No. 8603, V-5

Corning Glass Nos. 8871, 9010, Lab. No. 189CS, IV-11

Crepe, pale and compounds, IV-51

Cresylic-acid formaldehyde resins, IV-18, 19, 68, 70

"Crolite" No. 29, IV-4

Materials Index (cont.)

"Cronar," V-13,109

"Crowloy" 20, IV-7; V-217

"Crowloy" 70, IV-7

"Crowloy" BX113, IV-7; V-218

"Crowloy" BX114, IV-7; V-219

Crystals, inorganic, IV-1, 2, 72-77; V-1, 26-30, 133-135

Crystals, organic, IV-15

"Dacron"-filled plastics, V-8, 10, 12, 14, 110

"Darex" No. 3, 43E, X-34, X-43, IV-38

"DeKhotinsky" Cement, IV-56

"Diala" Oil, IV-66

Diallyl phenyl phosphonate resin, IV-48

"Diamonite" B-890, V-2, 42

"Diamonite" P-3142, V-2, 43

"Diamonite" P-3459, V-2, 44

"Diamonite" P-3530-40, V-3, 45

Diatomaceous-earth ceramic, IV-6, 101

Dibutyl sebacate, IV-62

Dichloronaphthalenes, mixture of the 1, 2-, 1, 4- and 1, 5-isomers, IV-58

Dichloropentanes Nos. 14 and 40, IV-63

2, 5-Dichlorostyrene, IV-64

Diisopropyl biphenyl, V-19

"Dilectene" 100, IV-21

"Dilecto" (hot punching) XXX-P-26, IV-19; V-80, 81

"Dilecto" ("Mecoboard"), IV-18; V-82, 83

"Dilecto" GB 112S, IV-27

"Dilecto" GB-112T, IV-31, 32; V-104

"Dilecto" GB-116E and GB-126E, V-14

"Dilecto" GB-181E, V-14, 114

"Dilecto" GB-261S, IV-26; V-93

"Dilecto" GM-1, V-8, 88

"Dilecto" GM-PE, V-12, 108

Dioctyl sebacate, IV-62

Diphenyl, see Biphenyl

Dow-Corning:

Fluids, 200, IV-66
500, IV-66
550, IV-67
710, IV-67

Grease, No. 4, IV-67
high vacuum, V-20

Molding cmpds, XM-3, IV-26
301, V-9, 94

Resins, 996, IV-26
2101, IV-26
2103, IV-26, 27
2105, V-9, 94
2106, V-9, 95-101

Silastics, 120, IV-54
125, IV-54
150, IV-54
152, IV-54
160, IV-54
167, IV-54
180, IV-54
181, IV-54, 126
250, IV-54, 126
6181, X4342, IV-55
6167, IV-55, 126
XF6620, IV-55; V-20
X6734, IV-55
7181, IV-55

Dow C-244, IV-36

Dow Experimental Plastic Q-166, Q-166 + Fiberglass, Q-200.5, IV-39

Dow Experimental Plastic Q-247.1, IV-36

Dow Experimental Plastic Q-344, IV-40

Materials Index (cont.)

Dow Experimental Plastic Q-406, IV-37, 117

Dow Experimental Plastic Q-409, IV-42

Dow Experimental Plastic Q-475.5, IV-40

Dow Experimental Plastic Q-764.6 and Q-767.2, IV-37

Dow Experimental Plastic Q-817.1, IV-37, 117

"Durez" 1601, natural, IV-17

"Durez" 11863, IV-20

"Durite" No. 500, IV-17

"Durite" No. 221X, IV-19

"Ecco" L65, V-11

"Eccofoam" GL, V-8

"Eccofoam" HiK (1000°F), V-7

"Eccofoam" HiK (500°F), V-14, 115

"Eccofoam" PS, V-10

"Eccosorb" HFX122, V-13, 237

"Eccosorb" HFX123, V-13, 238

"Eccosorb" HF155, HF680, HF853, HF1000, HF2050, V-13

"Eccosorb" MF110, MF112, MF114 and MF116, V-15

"Eccosorb" MF117, V-15, 242

E Resin, IV-50

Elastomers, IV-51-55; V-127-129

"Elvacet" 42A-900, IV-33

"Elvanol" 51A-05, 50A-42, 70A-05, 72A-05, 72A-51, IV-33

"Ensolite" M22240, M22239, 3036, IV-31

"Epon" Resin RN-48, IV-50

"Epon" 828, V-16, 116-125

"Epon" X-131, V-16

Epoxy resins, IV-49, 50, 125; V-14-16, 114, 126

Epoxy laminates with:

"Dacron," V-14

"Fiberglas," IV-50; V-14, 16, 22, 114, 124, 125

"Nylon," V-14

"Orlon," V-14

"Estawax," IV-57

"Ethocel" LT5, IV-25, 115; V-91

Ethyl alcohol, IV-62

Ethyl cellulose, IV-25, 115; V-91

Ethylene Glycol, IV-62

Ethylpolychlorobenzene, IV-64

"Ferramic" A, V-159, 191, 220

"Ferramic" B, V-160, 192, 221

"Ferramic" C, V-161, 193, 222

"Ferramic" D, V-162, 194, 223

"Ferramic" E, V-163, 195, 224

"Ferramic" G, V-164, 196, 225

"Ferramic" H, V-165, 197, 226

"Ferramic" H-1, V-4, 166, 198

"Ferramic" I, V-167, 227

"Ferramic" J, V-168, 199, 228

"Ferramic" K, V-169, 229

"Ferramic" N, V-200

"Ferramic" Q (rec'd Dec. 1953), V-170, 230

"Ferramic" Q (rec'd Aug. 1954), V-171, 201, 231

"Ferramic" MF874, V-172, 202

"Ferramic" 1118, V-173, 232

"Ferramic" 1326B, V-174, 203

"Ferramic" 1331, V-175, 204, 233

"Ferramic" 3310 (experimental), V-176

Materials Index (cont.)

Ferrites, IV-7; V-4, 54, 133-204, 206-233

"Ferrotron" 119, V-17, 205, 244

"Ferrotron" 308, 309, V-18

"Ferroxcube" 105, V-4

"Fiberfrax" Board, V-6, 78

"Fiberglas" laminates, IV-16, 18, 22, 25-27, 31, 32, 47-50, 68; V-8-11, 13, 14, 16, 22, 86-88, 93-95, 98-101, 104

"Fiberglas" BK-174, laminated, IV-16

"Fibestos" 2050TVA C-1686, IV-24

"Foamglas," IV-11

Formaldehyde resins, aniline, IV-21

Formaldehyde resins, benzo-guanamine, IV-23

Formaldehyde resins, cresol, IV-18, 19, 68, 70

Formaldehyde resins, melamine, IV-21, 22, 112

Formaldehyde resins, phenol, IV-15-19, 109-111

Formaldehyde resins, phenol-aniline, IV-20

Formaldehyde resins, urea, IV-23

"Formica" FF-41 (sheet, rod stock), IV-21, 68

"Formica" FF-55, IV-21, 69

"Formica" G7, G6, IV-25

"Formica" Grade MF-66, IV-20, 68

"Formica" XX, LE, IV-17, 68

"Formica" YN-25, IV-17

"Formica" Z65, IV-46

"Formica" Z80, IV-47

"Formvar," Type E, IV-34

"Forticel" No. 28102, IV-25; V-90

"Forticel" JLB-(H), V-9

"Forticel" JMB-(M), V-9

"Fortiflex" A, V-10

"Fotoceram" (843 GU) and (843 GZ), V-5

"Fotoform" B(843 GU), B(843 GZ), C(843 GU), C(843 GZ), E(843 GU), and E(843 GZ), V-5

"Fractol" A, IV-66

Frenchtown 4462, IV-6; V-3, 48

Frenchtown 6096, V-3, 48

Frenchtown 7873, V-3, 49

Furfuraldehyde resin, phenol, IV-19

"Gafite" cast polymer, IV-34

Gasoline, aviation, 100 and 91 octane, IV-65

General Ceramics ADH-211, V-3

General Ceramics BM3054, V-4, 55

General Ceramics 7294, IV-4, V-55

General Ceramics "Ferramics", see "Ferramics"

Geon 2046, 80365, 80384, IV-29

Gilsonite, IV-56

Glasses, IV-9-12, 101-105; V-5, 6, 62-73

Glass, alkali-silica, IV-12, 105

Glass, alkaline lead silicate, IV-11

Glass, aluminum borosilicate, IV-10

Glass, aluminum zinc-phosphate, IV-9

Glass and mica, IV-13, 69, 106-108

Glass and plastic mixtures, IV-41, 42

Glass, barium borosilicate, IV-10

Glass, borosilicate, IV-9, 101

Glass, "E", IV-11

Glass, iron-sealing, IV-9, 102

Glass Lamicoid No. 6038, IV-21, 70

Materials Index (cont.)

Glass, lead-barium, IV-9

Glass, lime-alumina-silicate, IV-9

Glass, low alkali, potash-lithia-borosilicate, IV-10, 102; V-62, 63

Glass, phosphate 2043x, 2279x, IV-9

Glass, potash-lead-silicate, IV-9

Glass, potash-soda-barium-silicate, IV-9

Glass, silica, IV-10, 103; V-64

Glass, soda-borosilicate, IV-9, 10

Glass, soda-lead-borosilicate, IV-10

Glass, soda-lime-silicate, IV-9, 11

Glass, soda-potash-borosilicate, IV-9

Glass, soda-potash-lead-silicate, IV-9

Glass, soda-potash-lithia-borosilicate, IV-10

Glass, soda-silica, IV-11

"Glastic" GF, MM, MP and A-2, IV-48

"Glastic" S and MF, IV-47

"Glyptol" No. 1201 (red), IV-48

Grease, hi-vacuum, V-20

Grease, "KEL-F" No. 40, IV-63

GR-I (butyl rubber) and compound, IV-52

GR-S (Buna S) and compounds, IV-52

Gutta-percha, IV-51

"Halowax" No. 1001, IV-57

"Halowax" No. 11-314, IV-58

"Halowax" Oil 1000, IV-64

Heptacosafluorotributyl, IV-63

Heptane, IV-62

Hexachlorobutadiene, IV-62

Hexamethylene-adipamide polymer, IV-23, 113

Hexane, V-19

Hooker 32A, V-13

"Hycar" OR "Cell-tite," IV-52

Hydrocarbon polymer, cross-linked, IV-50

Hydrocarbons, petroleum, IV-65, 66

12-Hydroxystearin, IV-58

"Hysol" 6000 and 6020, IV-50

"Hysol" 6000 HD, V-15, 126

"Hysol" 6030, IV-50, 70

"Hysol" 6030-B, V-15

"Hysol" XL-6060, V-15

"Hysol" XE-6080, V-16

"Hy-tuf" Laminate Grade GF181, IV-50

Ice, IV-1

Ignition Sealing Compound No. 4, IV-67

Iron and plastic mixtures, IV-43, 44; V-243

Iron-manganese oxide and plastic mixtures, IV-45

Irvington tape, V-17

Isobutylene-isoprene copolymer, IV-52

Jet fuel JP-1 and JP-3, IV-65

Jet fuel JP-4, V-19

Kearfott alumina, V-3, 46, 47

"Kel-F," IV-31

"Kel-F" Alkanes 464, 695, V-18

"Kel-F" Alkanes 8126, 10157, 12188, V-19

Materials Index (cont.)

"Kel-F" Grade 300 and 300-P25, IV-31, 116

"Kel-F" X200, V-10, 102, 103

"Kel-F" Grease No. 40, IV-63

"Kel-F" Oil, Grade No. 1 and No. 3, IV-63

"Kel-F" Oil, Grade No. 10, IV-63; V 130, 131

"Kel-F" Wax No. 150, IV-58

Kerosene, IV-65

"Koroseal" 5CS-243, IV-30

"Kralastic" BE, BM, D, EBMU, F, IV-53

KRS-5, IV-2, 76

KRS-6, IV-2, 75

"Laminac" 4115, IV-46, 120

"Laminac" 4-205, IV-46, 121

"Laminac" 4232, V-106, 107

"Laminac" PDL7-627 and PDL7-650, IV-46, 120

Laminates and impregnated batts, see filter or resin:

- Asbestos-filled plastics
- "Dacron"-filled plastics
- Epoxy laminates
- "Fiberglas" laminates
- Melimine GMG
- "Nylon"-filled plastics
- "Orlon"-filled plastics
- Ppper laminates
- Phenolic Resin plus fillers
- Polyester resin plus fillers
- Polystyrene plus fillers
- Silicone resin plus fillers

"Laminate" BD-44 and BK 164, IV-47, 48

Lava, V-21, 75

Leather, sole , IV-60

Liquids, aliphatic, IV-62, 63; V-18, 19. 130, 131

Liquids, aromatic, IV-63, 64; V-19

Liquids, inorganic, IV-61; V-18

Liquids, organic, IV-62-67; V-18, 19, 20

Liquids, petroleum, IV-65, 66

Liquids, silicone, IV-66, 67; V-20

Lithium fluoride, IV-1

Lithium-nickel ferrite (M.I.T. samples), V-137, 178

"Loalin," IV-36

"Lucite" HC-202, V-10

"Lucite" HM-119 and HM-140, IV-34, 70

"Lucite," sintered, IV-34

"Lucoflex," IV-30

"Lumarith" XFA-H4 and 22361, IV-24, 25, 70

"Lustrex" loaded glass mat, IV-41

Magnesium ferrite (M.I.T. samples), V-138, 179, 207

Magnesium-manganese ferrite (M.I.T. samples), V-139, 140, 180, 181, 208

Magnesium-manganese-zinc ferrite (M.I.T. samples), V-141, 182

Magnesium manganite, V-4, 54

Magnesium oxide, IV-1; V-29

Magnesium silicate, IV-3, 78-82

Magnesium titanate, IV-4

Magnesium titanate and plastic mixture, IV-43

Magnetite and plastic mixtures, IV-44, 45

Manganese-magnesium ferrite (M.I.T. samples), V-139, 140, 180, 181, 208

Materials Index (cont.)

Manganese-magnesium-zinc ferrite (M.I.T. samples), V-141, 182

Marble S-303, IV-13

"Marbon" S, Buna S Hardboard, IV-52

"Marbon" S (Code 7206), S-1 (Code 7254), 8000 and 9200, IV-38

Marco Resin "MR"-21C, "MR"-23C and "MR"-25C, IV-47

"Marcol," IV-65

"Markite" 3985, V-20, 235

"Markite" 12812, V-20, 236

"Marlex" 50, V-10

Mathieson Plastic CY-8 and CQ-10DM, IV-41

Meat, IV-60

"Mecoboard," IV-18; V-82-83

Melamine-formaldehyde resins, IV-21, 22, 112; V-8, 88

Melamine GMG, IV-21, 70

"Melamac" 7278 + "E" glass, IV-22

"Melmac" Molding Comp. 1500, 1502, IV-22, 112

"Melmac" Resin 592, IV-21

"Melmac" Type 1077 (Ivory WB 48), IV-21

Methacrylate resins, IV-34, 35

"Methocel," IV-25

Methyl alcohol, IV-62

Methyl cellulose, IV-25

Methylstyrene-styrene co-polymer, IV-39

Mica and glass, IV-13, 69, 106-108; V-7, 79

Mica, Canadian, IV-13

Mica-filled plastics, IV-16, 17, 18, 20

"Micaramic," V-7

Mica, ruby, IV-13

"Micarta" No. 254, IV-18

"Micarta" No. 259, IV-22, 68

"Micarta" No. 299, IV-19, 68

"Micarta" No. 496, IV-18, 68, 70

"Millimar," IV-56

Minn. Mining EC-612, V-17

"Missileon," V-17

Monoisopropyl biphenyl, V-19

Monsanto OS-45, OS-59 and OS-82, V-19

Morse 200, V-16

Morse 280, 300, 400, 6060-C and 6062, V-17

Muscovite, IV-13

"Mycalex" K10, IV-13

"Mycalex" 400, IV-13, 69

"Mycalex" 2821, IV-13, 106, 107

"Mykroy" Grade 8 and 38, IV-13, 108

"Mylar" A, V-13

Naphthalene, IV-15

Naphthalene, chloro-, IV-64

Naugatuck Laminating Resin MP and MT, IV-47

Neoprene GN and compound, IV-53

Nickel ferrite (M.I.T. samples), V-133-135, 142, 143, 183, 209

Nickel-lithium ferrite (M.I.T. samples), V-137, 178

Nickel-zinc ferrite (M.I.T. samples), V-144-157, 184-190, 210-216

Nitrobenzene, IV-64

Materials Index (cont.)

Nitrogen, gas, V-20

Nitrogen, liquid, V-18

Nitrous oxide gas, V-20

Norton 7X, V-3, 49

Norton 17Z, V-3

"Nylon" 66 and 610, IV-23

"Nylon" FM 10, 001, IV-23, 113; V-89

"Nylon"-filled plastics, IV-17; V-8, 12, 14, 82, 83

Oil, HB-40, IV-63

Oils, petroleum, IV-65, 66

"Opalwax," IV-58

"Orlon"-filled plastics, V-8, 10, 12, 14

Owens-Corning CR-262, 57M, EA63, EA73, X600, V-6

"Ozokerite," IV-58

Panelyte Grade 140 and 776, IV-17, 22

Paper, Kraft, V-18

Paper laminates, IV-17-19, 21-23, 46; V-80

Paper, Royalgrey, IV-60

Paraffin, natural, IV-58

Paraffin Wax 132° ASTM and 135° AMP, IV-58

"Paraplex" P13, IV-48, 122

"Paraplex" P43, IV-48; V-12, 111

"Parowax," IV-58

"Pelron" 9420, 9422, 9423 and 9424, V-11

"Penton," V-16

Perfluorodihexyl ether, IV-63

"Permafil," 3256, IV-50

"Permo" potting Compound No. 49 and No. 51, IV-49, 51

Petroleum oils, IV-65, 66

Phenol-aniline-formaldehyde resins, IV-20

Phenol-formaldehyde resins, IV-15-19, 109-111

Phenol-furfuraldehyde resin, IV-19

Phenolics, IV-15-20, 109-111; V-8, 80-87

Phenolic, Expanded, IV-19

Phenilic paper laminate JH-1410, IV-18

Phenolic resin with asbestos, V-8, 84, 85

Phenolic resin with "Dacron," V-8

Phenolic resin with "Fiberglas," V-8, 86, 87

Phenolic resin with "Nylon," V-8

Phenolic resin with "Orlon," V-8

Phenolic spheres, V-12

"Phoresin," IV-48

"Piccolastic" D-125, IV-39

"Piccopale," Resin, IV-50

Pipestone, V-7

"Plaskon" 911, IV-47

"Plaskon" Alkyd 411, 420, 422, 440, 440A and 442, IV-49

"Plaskon" Alkyd Special, Electrical Granular, IV-49, 123; V-112, 113

"Plaskon" melamine, IV-22

"Plaskon" Urea, natural and brown, IV-23

"Plasticell," IV-31

"Plast-Iron" and plastic mixtures, IV-43, 44

"Plexiglass," IV-34

"Plicene" Cement, IV-56

Materials Index (cont.)

"Pliobond" M-190-C, IV-52

"Pliolite" and Pliolite GR, IV-51

"Pliolite" S5, S3, S6B and S6, IV-40

Polaroid Resin C, IV-40

"Polectron" No. 24, IV-46

"Policap," V-16

"Polinel," IV-58

Polyamide resins, IV-23, 113; V-8, 12, 14, 82, 83, 89

Polybutene, IV-59

Polybutyl methacrylate, IV-35

Poly-2-chlorobutadiene-1, 3, IV-53

Polychlorostyrenes, IV-41, 42

Polychlorotrifluoroethylene, IV-31, 58, 63, 116; V-10, 102, 103

Polycyclohexyl methacrylate, IV-35

Polycyclostyrene, V-11

Polydiallyl phthalate, IV-48

Poly-2, 5-dichlorostyrene, IV-40-42, 70

Poly-2, 5-dichlorostyrene + fillers, IV-42-45; V-243

Poly-3, 4-dichlorostyrene, IV-42

Polyesters, IV-46-48, 120-123; V-11, 12, 13, 106-111

Polyester resin with "Dacron," V-12, 110

Polyester resin with "Fiberglas," IV-47, 48; V-12, 13, 22, 106, 107, 108

Polyester resin with "Nylon," V-12

Polyester resin with "Orlon," V-12

Polyester resin with phenolic spheres, V-12

Polyether, chlorinated, V-16

Polyethyl methacrylate, IV-35

Polyethylene, IV-27, 28, 70; V-10

Polyethylene (effect of milling), IV-28

Polyethylene DE-3401, IV-27

"Polyglas" D^+, IV-42

"Polyglas" M, IV-22

"Polyglas" P^+, IV-41

"Polyglas" S, IV-26

Polyisobutyl methacrylate, IV-35

Polyisobutylene B-100 + Marbon B, IV-28

Polyisobutylene, Run 5047-2, IV-28

Polymethyl methacrylate, IV-34, 70; V-10

Polysiloxane resin, IV-26, 27; V-9

Polystyrene, IV-35-37, 117

Polystyrene, cast in vacuo and cast in air, IV-37

Polystyrene + chlorinated diphenyl, IV-37

Polystyrene, cross-linked, IV-39, 40, 119; V-11, 105

Polystyrene Fibers Q-107, IV-37

Polystyrene + fillers, IV-41; V-10, 239, 240

Polystyrene Foam Q-103, IV-37

Polystyrene, hydrogenated, IV-46

Polystyrene, α-methylstyrene, IV-37, 117

Polytetrafluoroethylene, IV-31-33, 70; V-10, 104

Polytrifluorostyrene, V-11

"Polythene" A-3305, IV-27, 70

Polyvinyl acetal, IV-34

Polyvinyl acetate, IV-33

Polyvinyl alcohol-acetates, IV-33

Materials Index (cont.)

Polyvinyl butyral, IV-34

Poly-N-vinylcarbazole, IV-46

Polyvinyl chloride 1006, 1018, 1216, 1406, W-174, W-175 and W-176, IV-30

Polyvinyl chloride-acetate, IV-28-31

Polyvinyl chloride-acetate + plasticizer, IV-28, 29

Polyvinyl chlorides, IV-28-31; V-10

Polyvinylcyclohexane, IV-46

Polyvinyl formal, IV-34

Polyvinylidene and vinyl chlorides, IV-31

Poly-α-vinylnaphthalene, IV-46

Poly-2-vinylpyridine, IV-46

Polyvinyl resins, IV-27-46

Polyvinyltoluene, IV-37, 117

Poly-p-xylylene, IV-37

Porcelain, wet and dry process, IV-6, 100

Porcelain No. 4462, IV-6

Porcelains, IV-6, 94-100; V-2, 3, 5, 21, 40, 59-61

Porous Ceramic AF-497, IV-6, 101

Potassium bromide, IV-1

Potassium chloride, V-1

Potassium dihydrogen phosphate, IV-1, 73

"Primol"-D, IV-66

n-Propyl alcohol, IV-62

"Prystal," IV-17

"Pyralin," IV-25

"Pyranol" 1467, 1476 and 1478, IV-63, 64

"Pyrex," IV-10

"Pyrotex," V-8

Quartz, fused, IV-11, 104; V-6, 72, 73

"Quinorgo" No. 3000, IV-13

"Quinterra," IV-13

Raytheon 402B, V-3

"Resimene" 803-A, IV-22

"Resinox" 7934, IV-20

"Resinox" 10231, IV-18, 109

"Resinox" 10900, IV-18, 110

Resins, natural, IV-55, 56

"Rexolite" 1422, IV-40; V-105

"Rexolite" 2101, V-11

"Rocketon," V-17

"Royalite" 149-11, M21982-1 and M22190, IV-53

Rubber, butyl (GR-I), IV-52

Rubber, cellular, IV-51

Rubber, cyclized, IV-51, 52

Rubber, GR-S (Buna S) and compounds, IV-52

Rubber, Hevea and compounds, IV-51

Rubber, natural, IV-51

Rubber, nitrile, IV-53

Rubber, silicone, IV-54, 55, 126; V-127-129

Rutgers' wallastonite E16, V-4

Rutile, IV-2, 4, 77

S-40 and S-60 resins, IV-39

"Santicizer" 9, IV-15

Sapphire, IV-72; V-1, 26, 27, 28

"Saran" B-115, IV-31

Savereisen Cement No, 1, V-7

"Scotchply" type 1001, V-16

"Scotchply" type 1002, V-22

Materials Index (cont.)

"Scotchply" XPM-107, V-22

"Scotch" tape No. 39, V-17

Sealing Wax, Red Express, IV-58

Sealing compound, V-17

"Selectron" 5003 + glass, IV-47

"Selectron" 5084 monomer, V-19

"Selectron" 5084 resin, V-13

Selenium, amorphous, IV-13

Selenium, multi-crystalline, IV-1

Shellac, natural XL, IV-55

Shellac, natural Zinfo, pure C garnet and garnet dewaxed, IV-56

"Silastic" 120, 125, 150, 152, 160, 167 and 180, IV-54

"Silastic" 181 and 250, IV-54, 126

"Silastic" X4342, IV-55

"Silastic" 6167, IV-55, 126

"Silastic" 6181, X-6734 and 7181, IV-55

Silica, fused 915c, IV-11, 103; V-70, 71

Silicon dioxide, fused, IV-11, 103; V-70, 71

Silicon nitrite alloy, V-6, 79

Silicone Alloys C-1147 and C-1328, V-9

Silicone fluids DC200 and DC500, IV-66

Silicone fluids DC550 and DC710, IV-67

Silicone fluid DC XF-6620, V-20

Silicone fluids SF96-40, SF96-100 and SF96-1000, IV-67

Silicone glass laminates, IV-26, 27

Silicone grease, V-20

Silicone Molding Compound XM-3, IV-26

Silicone resin DC996 and DC2101, IV-26

Silicone resin DC301, V-9, 94

Silicone laminate DC2105, V-9, 94

Silicone laminate DC2106, V-9, 95

Silicone resins, IV-25-27; V-9

Silicone resins with asbestos, V-9, 96, 97

Silicone resins with "Fiberglas," V-9, 93-95, 98-101

Silicone rubbers, IV-54, 55, 126; V-127-129

Silicone rubber SE-450, IV-55; V-127

Silicone rubber SE-460, IV-55; V-128

Silicone rubber SE-555, IV-55

Silicone rubber SE-977, IV-55; V-129

Silicone varnish, IV-26; V-18

"Sintox," V-3

Snow, IV-1

Soap, IV-60

Sodium chloride, IV-2

Sodium chloride, aqueous solutions, IV-61

Soils, IV-14

Steak, IV-60

Steatite bodies, IV-3, 4, 78-87; V-4, 55-57

Steatite Body 7292, IV-4, 83

Steatite Type 302, 400, 410 and 452, IV-3, 84-87

Sterling M50 varnish on paper, V-18

Strontium titanate, IV-5

Strontium titanate and plastic mixtures, IV-43

Stupakoff 1510, V-3, 51

Materials Index (cont.)

Stupakoff 1540, V-3, 50

Stupakoff 1542E, V-3

Stupakoff 1542P, V-3, 50

Stupakoff 1550, V-4, 50

"Stycast" HiK, LoK and TPM-3, V-11

"Stypol" 16B monomer, V-19

"Stypol" 16B resin, IV-48, 123; V-110

"Stypol" 16C resin, IV-48

"Stypol" 16D resin, IV-48; V-12

"Styraloy" 22, IV-38

"Styramic" No. 18, IV-37

"Styramic" HT, IV-42, 43

Styrene copolymers, cross-linked, IV-39, 40, 119; V-11, 105

Styrene copolymers, linear, IV-38, 39, 118, 119

Styrene dimer, IV-64

Styrene N-100, dry and saturated with water, IV-64

Styrene-acrylonitrile copolymer, IV-38, 53, 118

"Styrofoam" 103.7, IV-37

"Styron" C-176, 411-A, 475, 666 and 671, IV-36

Suet, IV-60

Sulfur, crystalline, IV-2

Sulfur, sublimed, IV-2

"Supramica" 500, V-7, 79

"Tam Ticon" B, BS, C, MC and S, IV-4, 5, 43

"Tam Ticon" T-S, T-L and T-M, IV-4

Taylor Grade GGG, IV-18, 111

Taylor Grade GSC and GSS, IV-27

"Teflon," IV-31-33, 70; V-24, 104

"Teflon" + calcium fluoride, IV-32; V-10

"Teflon" Laminate GB-112T; IV-31, 32

"Tenite" I 008A H_2, H_4, M, MH, S and S_4, IV-24

"Tenite" II 205A H_2, H_4, MH, MS, S_2, S_4, IV-24

Terphenyl, meta-, nona-, ortho- and para-, IV-15

Terphenyls, chlorinated, IV-64

Tetrachloroethylene, IV-62

Tetra alkyd silicate ester, V-19

Thallium bromide, IV-2, 75

Thallium bromide-chloride, IV-2, 75

Thallium bromide-iodide, IV-2, 76

Thallium chloride, V-1

Thallium iodide, IV-2, 74

Thermoplastic Composition 1766EX and 3738, IV-58

Thermoplastic Composition 3767A, IV-59

"Thiokol," Type FA, PRI and ST, IV-54

TI Pure R-200, IV-4

Titanate ceramics, IV-5, 6

Titania and titanate bodies, IV-4-6, 88-93

Titanium dioxide ceramics, IV-4, 5

Titanium dioxide, rutile, IV-2, 4, 77

Titanium dioxide + plastic mixtures, IV-33, 42

Toluene sulfonamides, mixture of ortho- and para- isomers, IV-15

"Transil" Oil 10C, IV-65

Trichlorobenzenes, mixture of isomeric, IV-64

Materials Index (cont.)

Trichloronaphthalenes, mixture of isomeric, IV-64

α-Trinitrotoluene, IV-15

"Ultron" Wire Compound UL300, UL1004 and UL24001, IV-30

Union Carbide + Carbon R-63 Varnish, V-18

Urea-formaldehyde resins, IV-23

Varnished linen tape, V-17

Varnished paper, V-18

Varnished glass cloth, V-18

"Vaseline," IV-65

"Vibron" 140 and 141, IV-40

"Vinylite" QYNA, VG-5544 and VG-5901, IV-28

"Vinylite" VG-5904, VYHH, VYNS and VYNW, IV-29

"Vinylite" VU-1900, IV-29, 70

2-Vinylpyridine-styrene copolymer, IV-46

"Vistawax," IV-59

Water, conductivity, IV-61

Wax 3760, IV-59

Wax Compound F-590 and No. 1340, IV-59

Wax S-1167 and S-1184, IV-59

Waxes, IV-56-59; V-16, 17

"Wesgo" AL-300, V-4, 52

"Wesgo" Al-1009, V-4

Wollastonite, V-4, 58

Wood, IV-59

Zinc ferrite (M.I.T. samples), V-158

Zinc-magnesium-manganese ferrite (M.I.T. samples), V-141, 182

Zinc-nickel ferrite (M.I.T. samples), V-144-157

Zirconium porcelain Zi-4, IV-6, 94, 95

Zircons, IV-6, 94, 95; V-5, 59-61