


REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE April 17, 1995	3. REPORT TYPE AND DATES COVERED Technical (preprint)	
4. TITLE AND SUBTITLE Molecular Motion of Phosphazene-Bound NLO Chromophores		5. FUNDING NUMBERS N00014-91-J-1194 Dr. K. J. Wynne R&T Code: 3132007	
6. AUTHOR(S) Harry R. Allcock* and Charles G. Cameron (PSU) Timothy W. Skloss, Sharon Taylor-Meyers, and James F. Haw* (Texas A&M)			
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Department of Chemistry The Pennsylvania State University 152 Davey Laboratory University Park, Pennsylvania 16802		8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research 800 North Quincy Street Arlington, Virginia 22217-5000		10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES Prepared for publication in MACROMOLECULES			
12a. DISTRIBUTION / AVAILABILITY STATEMENT Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release; distribution is unlimited.		12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The behavior of NLO groups linked to a polyphosphazene chain was studied by solid state NMR spectroscopy. A series of poly(organophosphazenes) was prepared and characterized. Variable-temperature solid state ¹³ C NMR spectra indicated that the use of a longer spacer group between the polymer backbone and the aromatic portion of the NLO side group lowered the temperature at which chromophore motion is quenched. This implied that the use of such structures may accelerate the randomization of NLO side group orientation at ambient temperatures following poling. This behavior was mirrored in the solid state variable-temperature ³¹ p NMR spectra, which suggested that side chain and polymer backbone may be coupled.			

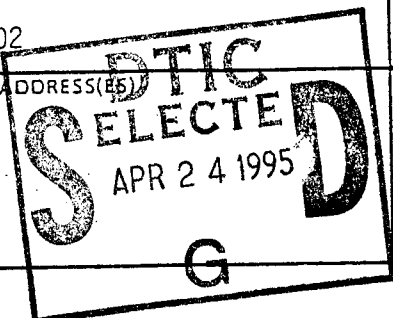

19950421 049

STANDARD FORM 298

14. SUBJECT TERMS Phosphazenes, polymers, electro-optical, nonlinear optical, NMR			15. NUMBER OF PAGES
			16. PRICE CODE
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT UL

OFFICE OF NAVAL RESEARCH

Grant No. N00014-91-J-1194

R&T Project 3132007

Dr. Kenneth J. Wynne, Program Manager

Technical Report No. 26

Molecular Motion of Phosphazene-Bound NLO Chromophores

by

Harry R. Allcock* and Charles E. Cameron

Department of Chemistry
The Pennsylvania State University
University Park, Pennsylvania 16802

and

Timothy W. Skloss, Sharon Taylor-Meyers, and James F. Haw*

Department of Chemistry
Texas A&M University
College Station, Texas 77843

Prepared for publication in *Macromolecules*

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

Molecular Motion of Phosphazene-Bound NLO Chromophores

Harry R. Allcock* and Charles G. Cameron

Department of Chemistry

The Pennsylvania State University

University Park, PA 16802

and

Timothy W. Skloss, Sharon Taylor-Meyers and James F. Haw*

The Department of Chemistry

Texas A & M University

College Station, TX 77843

Received _____

Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification _____	
By _____	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

Abstract: The behavior of nonlinear optical (NLO) groups linked to a polyphosphazene chain was studied by solid state NMR spectroscopy. A series of poly(organophosphazenes) was prepared with the general structure, $[NP(RN(CH_3)C_6H_4NO_2)_x(O\{CH_2CH_2O\}_2CH_3)_{2-x}]_n$, where $x < 0.5$ and the spacer group $R = O(CH_2)_2$, $O(CH_2)_6$, or $OCH_2(2\text{-pyrrolidino})$ in addition to the stilbene-containing polyphosphazene, $[NP\{O(CH_2)_2N(CH_3)C_6H_4CH=CHC_6H_4NO_2\}_{0.4}\{O(CH_2CH_2O)_2CH_3\}_{1.6}]_n$. Structural characterization for the above polymers was achieved by ^{31}P NMR spectroscopy, differential scanning calorimetry and elemental microanalysis. Methoxyethoxyethoxy (MEE) cosubstituent poly(organophosphazenes) bearing $O(CH_2)_2N(CH_3)C_6H_4NO_2$ and $O(CH_2)_6N(CH_3)C_6H_4NO_2$ side groups were

selected for study by room-temperature and variable-temperature solid state ^{31}P and ^{13}C NMR spectroscopy. The variable-temperature solid-state ^{13}C NMR spectra indicated that the use of a longer spacer group between the polymer backbone and the aromatic portion of the NLO side group lowered the temperature at which chromophore motion is quenched. This implied that the use of such structures may accelerate the randomization of NLO side group orientation at ambient temperatures following poling. This behavior was mirrored in the solid state variable-temperature ^{31}P NMR spectra which suggested that side chain and polymer backbone motion may be coupled.

Introduction.

A growing interest exists in the design and synthesis of polymeric materials for use in nonlinear optical (NLO) applications.¹ The synthesis of such materials has been accomplished in two ways. First, a small-molecule chromophore may be dissolved in a glassy,^{2,3} or crystalline polymer.⁴ Second, NLO-active groups can be covalently linked to macromolecules by either radiative cross-linking⁵ to a host polymer, by derivatization of a functionalized polymer,^{6,7} or by macromolecular substitution reactions.⁸ The occurrence of NLO effects is associated with an intramolecular charge transfer process which can exist in organic molecules with a donor-acceptor moiety. For second harmonic generation (SHG), or the conversion of light of frequency ν to light of frequency 2ν , non-centrosymmetric alignment of the donor-acceptor moieties (usually by electric field poling) is required. In the absence of a method of stabilization of the alignment, SHG is lost quickly as orientational randomization of the donor-acceptor moieties occurs.⁸ The rate of orientational randomization is some function of the quasi liquidity in the polymeric material, which in turn is connected with macromolecular flexibility and the free volume. Randomization of the NLO components is normally considered to be a detrimental property unless the material forms part of a device in which electric field generated alignment forms part of a working component.^{1e}

Methods used to stabilize SHG in host - guest systems and in polymers that incorporate NLO groups as side chains include both a "freezing" of the alignment by cooling of the polymer or by radiation cross-linking, but these approaches generate additional challenges. An example of the first technique exists when the chromophore is poled in a host polymer above its T_g . "Flash cooling" to below the T_g is then carried out in an attempt to maintain the chromophore orientation. This method yields only modest success. For example, when 4-(dimethylamino)-4'-nitrostilbene is dissolved in poly(methyl methacrylate) and poled at 383 K, the system loses 80% of the SHG in 12 h after the

material is allowed to cool to 298 K.² Radiation cross - linking has been applied to polymers that contain side group NLO chromophores. For example, Tripathy, et. al.⁵ reported considerable success in stabilizing cinnamate-derivatized NLO chromophores by irradiation with UV light while poling.

Thus, an understanding of chromophore motions in unpoled systems in the region of the T_g should yield insights into the molecular motions of poled polymers. In this work we have attempted to obtain an insight into this phenomenon through the synthesis and solid state NMR characterization of polyphosphazenes that bear pendent NLO chromophore side groups.

Polyphosphazenes have several advantages for the study of chromophore motion in polymeric materials. These include: (1) different cosubstituent groups can be readily incorporated into polyphosphazenes by macromolecular substitution, and this allows properties such as the T_g to be tailored over a broad range; (2) the relative ease of side group incorporation allows a wide variety of NLO chromophores to be covalently linked to the polymer backbone, and provides a vehicle for the products to be examined by solid-state NMR; (3) the phosphorus - nitrogen backbone contains no carbon atoms; hence, ^{13}C NMR studies of pendent side chains are not complicated by the backbone elements; (4) the polymer backbone motion can be studied unambiguously by solid-state ^{31}P NMR spectroscopy. In this paper we discuss the synthesis of mixed-substituent poly(organophosphazenes) that bear chromophores **1 - 4** (see Chart 1) and analyze the chromophore motion of polymers **8** and **9** (see Scheme 1) by solid-state variable-temperature NMR.

Chart 1 and Scheme 1 near here

Results and Discussion

Side Group Synthesis. Chromophores **1-3** were prepared^{7,9-11} by the reaction between 4-fluoronitrobenzene and the appropriate amine in DMSO solvent in the presence of K_2CO_3 as a hydrofluoride acceptor (see Scheme 2). Chromophore **4** was synthesized

in two steps (see Scheme 3). First, 4-fluorobenzaldehyde was allowed to react with N-(methylamino)ethanol under the above conditions to give intermediate aldehyde **11**. Stilbene **4** was obtained by the condensation of **11** with 4-nitrophenylacetic acid. Chromophores **1 - 4** were characterized by ^1H and ^{13}C NMR spectroscopy and mass spectrometry (see the Experimental section).

Schemes 2 and 3 near here

Polymer Synthesis. The synthetic route to high polymeric phosphazenes **7-10** is shown in Scheme 1. Poly(dichlorophosphazene) (**6**) was prepared by the thermal ring-opening polymerization of hexachlorocyclotriphosphazene (**5**).¹²⁻¹⁴ The substitution reactions of **6** were carried out in three steps. The synthesis and purification of polymer **8** will be given as a representative example. Polymer **8** was prepared by allowing 1 equiv of sodium methoxyethoxyethoxide to react with **6** to form a partially-substituted polymer with the idealized structure $[\text{NPCl}\{\text{O}(\text{CH}_2\text{CH}_2\text{O})_2\text{CH}_3\}]_n$. This macromolecular intermediate was then treated with 0.5 equiv of the sodium salt of **1** to replace approximately 50% of the remaining chlorine atoms. Lastly, a fully substituted, chlorine-free polymer was obtained by allowing an excess of $\text{Na}(\text{OCH}_2\text{CH}_2)_2\text{OCH}_3$ to replace all the remaining chlorine atoms to give a polymer with the idealized structure $[\text{NP}(\text{OCH}_2\text{CH}_2\text{N}(\text{CH}_3)\text{C}_6\text{H}_4 - p - \text{NO}_2)_{0.5}\{(\text{OCH}_2\text{CH}_2)_2\text{OCH}_3\}_{1.5}]_n$. Total chlorine replacement and side group loadings were confirmed by the elemental analytical data (see Table 1).

Table 1 Near Here

This synthetic route was used for several reasons: (1) The initial addition of the sodium salt of the chromophores to poly(dichlorophosphazene) in THF resulted in the formation of an insoluble precipitate which could not be induced to undergo further reaction. (2) The use of 2,2,2-trifluoroethoxy cosubstituents (side groups that were used in earlier phases of our NLO work⁸ and were found to generate soluble NLO polyphosphazenes) may bring about the displacement of NLO side groups during the

second step of the substitution reaction. (3) The ^{13}C resonance of the CF_3 carbon in the trifluoroethoxy side group is a quartet centered at ca 115 ppm, which overlaps the ^{13}C resonances of the aromatic ring in the NLO cosubstituent. (4) The glass transitions of methoxyethoxyethoxy cosubstituent polymers **7-10** are easily detected by DSC. These data are essential for the study of the molecular dynamics of polymers near the glass transition temperature.

Although the methoxyethoxyethoxy cosubstituent facilitates solid state NMR characterization, polymers **7-10** were insoluble in common organic solvents after isolation from the THF dialysis. This insolubility is attributed to the high polarity of the donor-acceptor side chains, which may result in stacking of the NLO groups in the solid state.^{15,16} This behavior is similar to that found in side-chain liquid crystalline polyphosphazenes.

Solid State NMR Studies.

Room Temperature ^{13}C NMR Spectroscopy. Polymers **8** and **9** were selected for detailed characterization by variable temperature ^{13}C and ^{31}P magic angle spinning (MAS) NMR. Since chromophore orientation is a requirement for second-order NLO polymers, the focus of this investigation was on qualitative studies of side chain and main chain dynamics. Polymers **8** and **9** were very similar, with the exception of the number of carbon atoms in the spacer unit that connects the chromophore to the main chain (2 CH_2 's for **8** vs. 6 CH_2 's for **9**). At a given temperature, the chromophore with the longer spacer would be expected to be the more mobile species. This expectation was confirmed, but the room temperature and variable-temperature ^{31}P NMR results indicated an additional effect. The NMR results are reported below in detail for polymer **8**. The results for polymer **9** are then explained briefly with emphasis on the differences between the two materials.

The ^{13}C MAS NMR spectra obtained at room temperature for polymer **8** and crystalline chromophore **1** are compared in Figure 1. Peaks in the spectra of chromophores **1** and **3** were identified by comparison with solution spectra as well as by acquisition of interrupted decoupling spectra (not shown). The MAS spectrum of solid chromophore **1** showed two clear characteristics of a rigid molecule. The pairs C_3, C_5 and C_2, C_6 had different isotropic shifts due to their inequivalent locations in the unit cell. Secondly, the chemical shift anisotropy of the aromatic carbon atoms was unaveraged, as reflected by the intensities of the spinning sidebands. These features were absent from the ^{13}C MAS spectrum of polymer **8** at 298 K (Figure 1). Note that each pair C_3, C_5 and C_2, C_6 in the polymer collapsed to a single line, and that the sideband intensity is negligible. These results demonstrate that reorientation of the aromatic group in the macromolecular system with respect to its local chemical environment was rapid on a time scale of ca. 5 ms, and that its reorientation with respect to the direction of the applied magnetic field was rapid on a time scale of ca. 200 μs . These time scales are the reciprocals of the resonance frequency differences for the 2 and 6 carbons and the MAS spinning speeds, respectively.

Figure 1 near here

Variable Temperature ^{13}C NMR Spectroscopy. Variable temperature ^{13}C MAS spectra of polymer **8** were obtained using both Bloch decay and cross polarization¹⁷ over a temperature range of 153 to 298 K and are reported in Figures 2 and 3 respectively. These two different types of spectra should be regarded as complementary. At lower temperatures, where the chromophore is immobile, the ^{13}C T_1 's of the aromatic carbon atoms were longer than the pulse delay used in the Bloch decay spectra, and the signals from these carbon atoms were absent because of saturation (see Figure 2). At higher temperatures, the mobility of the chromophore precluded efficient cross polarization of the aromatic carbons, but aromatic isotropic peaks and spinning sidebands were seen clearly at lower temperatures in the cross polarization spectra (see Figure 3).

The signals from the aromatic carbon atoms were very broad at intermediate temperatures in both types of spectra. In the Bloch decay spectrum at 253 K, the aromatic signals were barely recognizable, and they were broad in CP spectra above ca. 193 K. This behavior is well known in MAS NMR studies of mobile materials,^{18,19} and it was used previously to characterize the time scale of chromophore reorientation for a simple small-molecule doped polymer system.²⁰ Magic angle spinning provides coherent averaging of chemical shift anisotropy, while molecular motion is an incoherent averaging process. When both effects are present and operate at similar time scales, a conflict arises such that line narrowing does not occur. The aromatic ring in polymer **8** underwent large amplitude motion on a time scale of ca. 200 μ s in the vicinity of 233 K. The broadening of the 65-75 ppm signals from the MEE side chains at 233 K and below was attributed to a freezing in of conformational inequivalence.

Figures 2 and 3 Near Here

Variable Temperature ³¹P NMR Spectroscopy. The variable temperature ³¹P MAS spectra of polymer **8** (Figure 4) were readily assigned based on previous studies of phosphazene polymers in solution and in the solid phase.²¹⁻²³ Most of the ³¹P nuclei resonated at an isotropic shift of -8.0 ppm, but those with one MEE side chain and one chromophore side chain provided the downfield shoulder at -2.9 ppm. Careful line fitting indicated that the chromophore content is 8% of all side groups or 16% of all main chain units. Small spinning sidebands were evident at 298 K, but these became much more pronounced when the sample was cooled to 233 K and lower temperatures, which indicated that the polymer backbone became rigid at this temperature.

Figure 4 Near Here

The corresponding ¹³C and ³¹P spectra for polymer **9** (Figures 5-7) showed the same overall behavior. The notable difference was that the longer spacer group lowered by 30 to 40 degrees the temperature at which chromophore and main chain motion were quenched relative to the counterpart with a shorter spacer. Again, good correlation

existed between the temperature profiles observed for the ^{13}C and ^{31}P spectra, and this suggested that the chromophore and main chain motions may be coupled processes.

Figures 5 - 7 Near Here

Conclusions.

Several conclusions can be drawn from the room-temperature and variable-temperature solid-state ^{31}P and ^{13}C NMR spectra. The room temperature CP/MAS NMR spectrum of free chromophore **1** showed features characteristic of a rigid molecule, such as spinning sidebands and different isotropic shifts of carbon atom pairs C_3 , C_5 and C_2 , C_6 . When chromophore **1** was attached to a flexible polyphosphazene backbone as in polymer **5**, all the characteristics of a rigid molecule are lost and the aromatic group was found to be undergoing reorientation with respect to its local chemical environment on a time scale of ca. 5 ms. Moreover, chromophore reorientation with respect to the direction of the applied magnetic field is rapid on a time scale of 200 μs .

Variable-temperature solid state ^{31}P and ^{13}C NMR of polymer **8** yielded additional insights into the backbone and side chain motions, respectively. The use of Bloch decay in the solid state variable-temperature ^{13}C NMR spectra showed that the aromatic chromophore motion was quenched at ca. 233 K, which was confirmed by the complimentary technique of cross polarized ^{13}C NMR. A similar effect of temperature on the polymer backbone was noted at ca. 233 K when polymer **8** was subjected to solid state variable-temperature ^{31}P NMR.

Lastly, when polymer **9** was analyzed under the same conditions, both backbone and side chain motion were found to be quenched at ca. 30 to 40 degrees lower than for polymer **8**. This behavior was attributed to the more flexible spacer group in polymer **9**. However, because both chromophore and polymer backbone motion were affected at the same temperature in polymers **8** and **9**, chromophore and backbone motion may be a coupled process.

From the viewpoint of retention of NLO group orientation following poling, the results suggest the following: As expected, a polymer which possesses a longer spacer unit between the aromatic portion of the NLO side group and the backbone gives a material in which the NLO side groups are more mobile than when a shorter spacer group is present. Second, because polymer backbone and side group motions may be coupled, the use of a flexible skeletal system and mobile side groups to solubilize the polymer may be counter - productive with respect to the retention of NLO properties after poling. Thus, for the polymers studied, polymer **8** must be cooled to below 233 K and polymer **9** below 193 K before rapid chromophore randomization is eliminated, which implies a higher room - temperature mobility for the NLO groups of polymer **9**. Of course, the more flexible, and more rapidly randomized system may, in fact, be more appropriate for use in applications where the switching on and off of the poling field is an integral feature of the device.

Experimental.

Hexachlorocyclotriphosphazene **5** (provided by Ethyl Corp.) was recrystallized from heptane and sublimed (60 °C, 0.05 mmHg) before use. Poly(dichlorophosphazene) **6** was prepared according to a previously published procedure.⁶⁻⁸ Tetrahydrofuran was distilled from sodium benzophenone under an atmosphere of dry argon.

Methoxyethoxyethanol was distilled from calcium hydride before use. The other reagents (Aldrich, Lancaster, Pfaltz & Bauer) were used as received. All manipulations of chlorophosphazene reagents before substitution reactions were carried out under an inert atmosphere of dry argon by using standard Schlenk and drybox techniques. Dialysis was accomplished with Spectra-Por cellulose membranes (MW cutoff 12,000-14,000, VWR).

Solution-state high field ³¹P (146 MHz), ¹³C (90 MHz) and ¹H (360 MHz) NMR spectra were obtained with a Bruker WM360 spectrometer. Solution-state ¹³C (50 MHz) and ¹H (200 MHz) NMR spectra were also obtained with a Bruker WP200 spectrometer or a Bruker ACE200 spectrometer. Both ¹³C and ³¹P NMR spectra were proton decoupled unless otherwise specified. Liquid-state ³¹P NMR spectra were referenced to external 85% H₃PO₄ with positive shifts recorded downfield from the reference. Solution-state ¹H and ¹³C NMR spectra were referenced to external tetramethylsilane.

Elemental analyses were by Galbraith Laboratories (Knoxville, TN). Chemical ionization (CI) mass spectra were obtained with a Kratos MS-25 spectrometer. Glass transition temperatures were determined by differential scanning calorimetry using a Perkin-Elmer 7 thermal analysis system equipped with a Perkin-Elmer 7500 computer. Heating rates of 10 - 40 °C/min. under a nitrogen atmosphere were used.

Room temperature ¹³C MAS NMR spectra of polymers **8** and **9** and the chromophores **1** and **3** were acquired on a CMX-360 spectrometer operating at 90.5 MHz for ¹³C. Single pulse (Bloch decay) excitation experiments were performed on the polymer samples while spinning at 2000 Hz. Cross polarization experiments were carried

out with the chromophore samples spinning near 5000 Hz. ^{13}C and ^{31}P variable temperature studies on polymers **8** and **9** were performed on a Chemagnetics CMX-300 instrument with the samples spun at a controlled rate of 2700 Hz. The samples were cooled to $-120\text{ }^{\circ}\text{C}$ and were then incrementally raised in temperature with at least 5 minutes equilibration time before the first experiment. Reproducible results without any detectable hysteresis were obtained from multiple temperature cycles. Both single pulse (10 s recycle delay) and CP experiments (4 ms contact time, 1s recycle delay) were acquired in the variable temperature study. Reduction of background signal from the Vespel MAS spinning module was accomplished by the use of composite excitation pulse sequences²⁴ in all CP and Bloch decay experiments.

Synthesis of 4-[2-hydroxyethyl)methylamino]nitrobenzene (1): Compound **1** was prepared by a modified literature procedure.^{7,9-11} 4-Fluoronitrobenzene (10.0 g, 70.9 mmol) and K_2CO_3 (10.0 g, 70.9 mmol) were added to DMSO (100 mL). *N*-methylaminoethanol (6.0 g, 80 mmol) was added over 10 min with stirring. The reaction mixture was warmed to $60\text{ }^{\circ}\text{C}$ for 12 h, after which it was poured into water (500 mL). The yellow precipitate was collected by vacuum filtration, washed with water (500 mL), and recrystallized from toluene. ^1H NMR (CDCl_3 , 200 MHz) 8.1 (d, 2H), 6.6 (d, 2H), 3.85 (q, 2H), 3.6 (t, 2H), 3.1 (s, 3H), 2.0 (t, 1H). ^{13}C NMR (CDCl_3) 153.8, 137.0, 126.2, 110.4, 60.0, 54.4, 39.4. MS *m/z* calcd 196, *m/z* found 197 (CI, MH^+). Yield: 89%. mp $101.5\text{-}102.5\text{ }^{\circ}\text{C}$.

Synthesis of 1-(4-nitrophenyl)-2-pyrrolidinemethanol (2)²⁵ and 4-[6-hydroxyhexyl)methylamino]nitrobenzene (3): Compounds **2** and **3** were prepared in a manner similar to compound **1**, with the use of (s) -(+) -pyrrolidine - 2- methanol for **2** and 6-(methylamino)hexanol for **3**. Characterization for **2**: 53% yield ^1H NMR (300 MHz, CDCl_3) 8.1 (2H, d, $J = 9\text{ Hz}$), 6.6 (2H, d, $J = 9\text{ Hz}$), 4.0 (1H, q, br.), 3.7 (1H, m), 3.6 (2H, m), 2.1 (4H, m), 1.5 (1H, t, $J = 6\text{ Hz}$). ^{13}C NMR ($\text{DMSO} - d_6$) 151.8, 135.2, 125.9, 111.2, 60.5, 60.3, 48.3, 27.7, 22.4. mp $114\text{-}116\text{ }^{\circ}\text{C}$ (Lit. mp, $116\text{ }^{\circ}\text{C}$). MS *m/z*

calcd 222, m/z found, 222 (EI, M^+). Characterization for **3**: ^1H NMR (300 MHz, CDCl_3) 8.1 (2H, d, $J = 8$ Hz), 6.6 (2H, d, $J = 8$ Hz), 3.6 (2H, q, $J = 6$ Hz), 3.4 (2H, t, $J = 7$ Hz), 3.1 (3H, s), 1.7 (4H, m), 1.6 (4H, m), 1.2 (1H, t, $J = 5$ Hz). ^{13}C NMR (90 MHz, CDCl_3) 153.5, 145.7, 126.3, 110.1, 62.7, 52.6, 38.7, 32.6, 26.9, 26.8, 25.6. MS m/z calc 252; m/z found 252 (EI). Anal Calcd. C, 61.90, H, 7.94, N, 11.11. Found, C, 62.01, H, 8.19, N, 10.88.

Synthesis of 2-[methyl[4-[2-(4-nitrophenyl)ethenylphenyl]aminoethanol (4): Stilbene **4** was synthesized according to a literature procedure.²⁶ ^1H NMR (CDCl_3 , 300 MHz) 8.2, 2H, d, $J = 9$ Hz), 7.6 (2H, d, $J = 9$ Hz), 7.4 (2H, d, $J = 9$ Hz), 7.2 (1H, d, $J = 16$ Hz), 6.9 (1H, d, $J = 16$ Hz), 6.8 (2H, d, $J = 9$ Hz), 3.9 (2H, q, $J = 6$ Hz), 3.6 (2H, t, $J = 6$ Hz), 3.1 (3H, s), 1.65 (1H, t, $J = 6$ Hz). ^{13}C NMR ($\text{DMSO} - d_6$) 145.2, 145.0, 128.6, 126.2, 124.0, 123.4, 120.7, 111.6, 58.1, 54.0, 38.5. MS m/z calcd 298.1317; m/z found 298.1321.

Synthesis of 4-[(2-hydroxyethyl)methylamino]benzaldehyde (11): Aldehyde **11** was prepared according to a literature procedure.²⁶ ^1H NMR (CDCl_3 , 300 MHz) 9.7 (1H, s), 7.7 (2H, d, $J = 8$ Hz), 6.8 (2H, d, $J = 9$ Hz), 3.9 (2H, d, $J = 6$ Hz), 3.6 (2H, d, $J = 6$ Hz), 3.1 (3H, s), 1.6 (1H, br). ^{13}C NMR (CDCl_3 , 75 MHz). MS m/z calcd, 196; m/z found 196 (EI).

Synthesis of polymers 7-10: The synthesis of polymer **8** will be given as a representative example. Fifty mL of a solution of sodium methoxyethoxyethoxide (prepared from methoxyethoxyethanol (2.06 g, 17.2 mmol) and sodium hydride (0.41 g, 17.2 mmol)) in THF (100 mL) was added over 2 min to a warm solution of poly(dichlorophosphazene) (1.0 g, 8.6 mmol) in THF (500 mL). The solution was stirred at 40 °C for 2 h and the sodium salt of **1** (prepared from alcohol **1** (1.68 g, 4.3 mmol) and NaH (0.10 g, 4.3 mmol) in THF (50 mL)) was added over 2 min and the again stirred at 40 °C for an additional 2 h. Finally, 50 mL of the solution of sodium methoxyethoxyethoxide was added and the solution was stirred overnight at room

temperature. The entire reaction mixture was dialyzed against water for 4 d and then against THF for 7 d. The polymer was isolated by rotary evaporation followed by vacuum drying at 50 °C overnight.

Acknowledgments. H. R. A. and C. G. C. thank the Office of Naval Research for the support of this work through Grant No. N00014-91J-1194. T. S., S. M. and J. F. H. thank the Office of Naval Research Grant No. N00014-91-J-1475.

References

1. (a) Chemla, D. S.; Zyss, J., Eds. *Nonlinear Optical Properties of Organic Molecules and Crystals*; Academic: New York, **1987**; Vols. 1, 2. (b) Khanarian, G., Ed. *Molecular and Polymeric Optoelectronic Materials: Fundamentals and Applications*; SPIE: San Diego, **1986**; Vol. 682. (c) Williams, D. J., Ed. *Nonlinear Optical Properties of Organic and Polymeric Materials*; ACS Symposium Series 233; American Chemical Society: Washington, D. C., **1983**. (d) Williams, D. S. *Angew. Chem., Int. Ed. Engl.* **1984**, *23*, 690. (e) Dagani, R. *Chem. Eng. News* **1995**, *73*(8) 28.
2. Hampsch, H. L.; Yang, J.; Wong, G. K.; Torkelson, K. M. *Macromolecules* **1988**, *21*, 526.
3. Singer, K. D.; Sohn, J. E.; Lalama, S. J. *Appl. Phys. Lett.* **1986**, *49*, 246.
4. Meredith, G. R. VanDusen, J. G.; Williams, D. J. *Macromolecules* **1982**, *15*, 1385.
5. Mandal, B. K.; Kumar, J.; Huang, J. C.; Tripathy, S. *Makromol. Chem., Rapid Commun.* **1991**, *12*, 63.
6. Ye, C.; Marks, T. J.; Yang, J.; Wong, G. K. *Macromolecules* **1987**, *20*, 2322.
7. Ye, C.; Minami, N.; Marks, T. J.; Yang, J.; Wong, G. K. *Macromolecules* **1988**, *21*, 2899.
8. Allcock, H. R.; Dembeck, A. A.; Kim, C.; Devine, R. L. S.; Shi, Y.; Steier, W. H.; Spangler, C. W. *Macromolecules* **1991**, *24*, 1000.
9. Kleb, K. G.; *Angew. Chem Int. Ed. Engl.* **1968**, *7*, 291.
10. Knipe, A. C.; Sridhar, N. *Synthesis* **1976**, 606.
11. Yilmaz, I.; Shine, H. J. *J. Labelled Compd. Radiopharm.* **1988**, *25*, 1157.
12. Allcock, H. R.; Kugel, R. L. *J. Am. Chem. Soc.* **1965**, *87*, 4216.
13. Allcock, H. R.; Kugel, R. L.; Valan, K. J. *Inorg. Chem.* **1966**, *5*, 1709.
14. Allcock, H. R.; Kugel, R. L. *Inorg. Chem.* **1966**, *5*, 1716.





15. (a) Allcock, H. R.; Connoly, M. S.; Sisko, J. T.; Al-Shali, S. *Macromolecules* **1988**, *21*, 323. (b) Allcock, H. R.; Mang, M. N.; Dembeck, A. A.; Wynne, K. J. *Macromolecules* **1989**, *22*, 323.
16. (a) Allcock, H. R.; Kim, C. *Macromolecules*, **1989**, *22*, 2596. (b) Allcock, H. R.; Kim, C. *Macromolecules*, **1990**, *23*, 3881.
17. Pines, A.; Gibby, M. G.; Waugh, J. S. *J Chem. Phys.* **1973**, *59*, 569.
18. Schaefer, J.; Stejskal, E. O.; Buchdahl, R. *Macromolecules* **1977**, *10*, 384.
19. Suwelack, D.; Rothwell, W. P.; Waugh, J. S. *J. Chem. Phys.* **1980**, *73*, 2559.
20. Taylor, S. A.; Ferguson, D. B.; Haw, J. F. *Macromolecules* **1992**, *25*, 2784.
21. Gabler, D. G.; Haw, J. F. *Macromolecules*, **1991**, *24*, 2794.
22. Maynard, Shawn J.; Sharp, T. R.; Haw, J. F. *Macromolecules*, **1991**, *24*, 2794.
23. Taylor, S. A.; White, J. L.; Elbaum, N. C.; Crosby, R. C.; Campbell, G. C.; Haw, J. F. Hatfield, G. R. *Macromolecules* **1991**, *24*, 2794.
24. White, J. L.; Beck, L. W.; Ferguson, D. B.; Haw, J. F. *J. Magn. Reson.* **1992**, *10*, 336.
25. Zyss, J.; Nicoud, J. F.; Coquillay, M. *J. Chem. Phys.* **1984**, *81*, 4160.
26. DeMartino, R. N.; Youn, H. N. U. S. Patent 4 808 332.

Figure Captions


1. Assigned ^{13}C MAS NMR of chromophore (**1**) and the chromophore-incorporated polymer (**8**) at room temperature. Asterisks denote spinning sidebands.
2. Variable temperature ^{13}C Bloch Decay MAS NMR spectra of polymer **8** (4s pulse delay, 400 transients). The expanded region shows the broadening of the aromatic chromophore signals with decreasing temperature.
3. Variable temperature ^{13}C CP-MAS NMR spectra of polymer **8** (4 ms contact time, 2s pulse delay, 800 transients). The expanded region shows a reappearance of the aromatic chromophore signal at 193 K.
4. Variable temperature ^{31}P Bloch Decay MAS NMR spectra of polymer **8** (10s pulse delay, 64 transients). Spinning sidebands are denoted by asterisks.
5. Variable temperature ^{13}C Bloch Decay MAS NMR spectra of polymer **9**. Broadening of the aromatic chromophore signals was seen at a lower temperature than for polymer **8**.
6. Variable temperature ^{13}C CP-MAS NMR spectra of polymer **9**. The expanded region shows a reappearance of the aromatic chromophore signal at a temperature 20 degrees lower (153 K) than for polymer **8**.
7. Variable temperature ^{31}P Bloch Decay MAS NMR spectra of polymer **9**. The spinning sidebands, denoted by asterisks, appear at a lower temperature (193 K) than for polymer **8**.

Table 1. Characterization data for polymers 7-10.


Polymer	Cosubstituent	T _g (K)	Cosubstituent Loading (%)	Exptl. Elem. Anal.			
				%C	%H	%N	%Cl
7	4	201	20	52.14	7.26	7.04	0.008
8	1	211	20	43.95	6.97	7.86	0.014
9	3	201	20	47.55	8.43	5.29	0.031
10	2	209	20	49.37	7.75	7.37	0.016

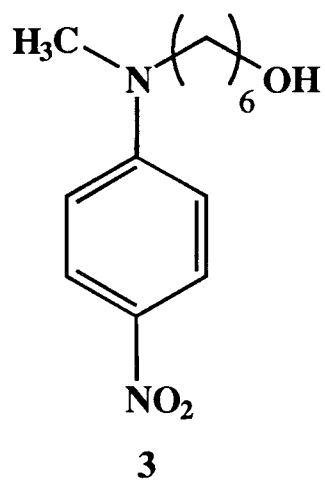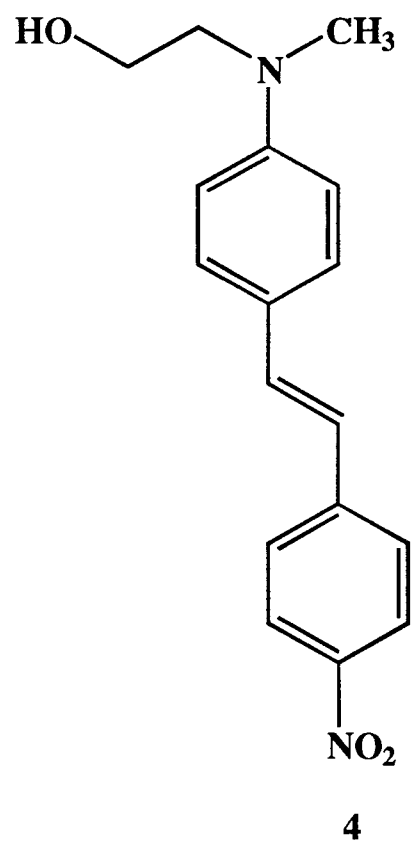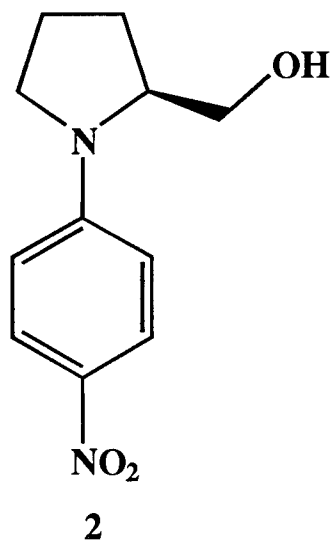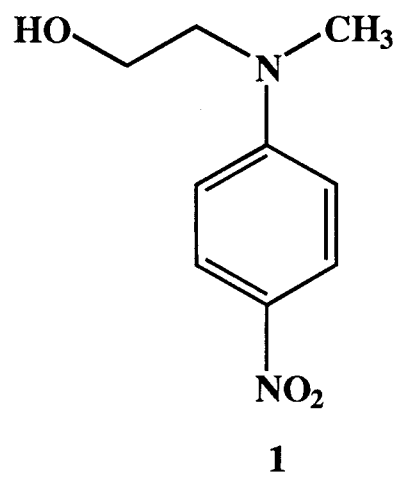


Scheme 1

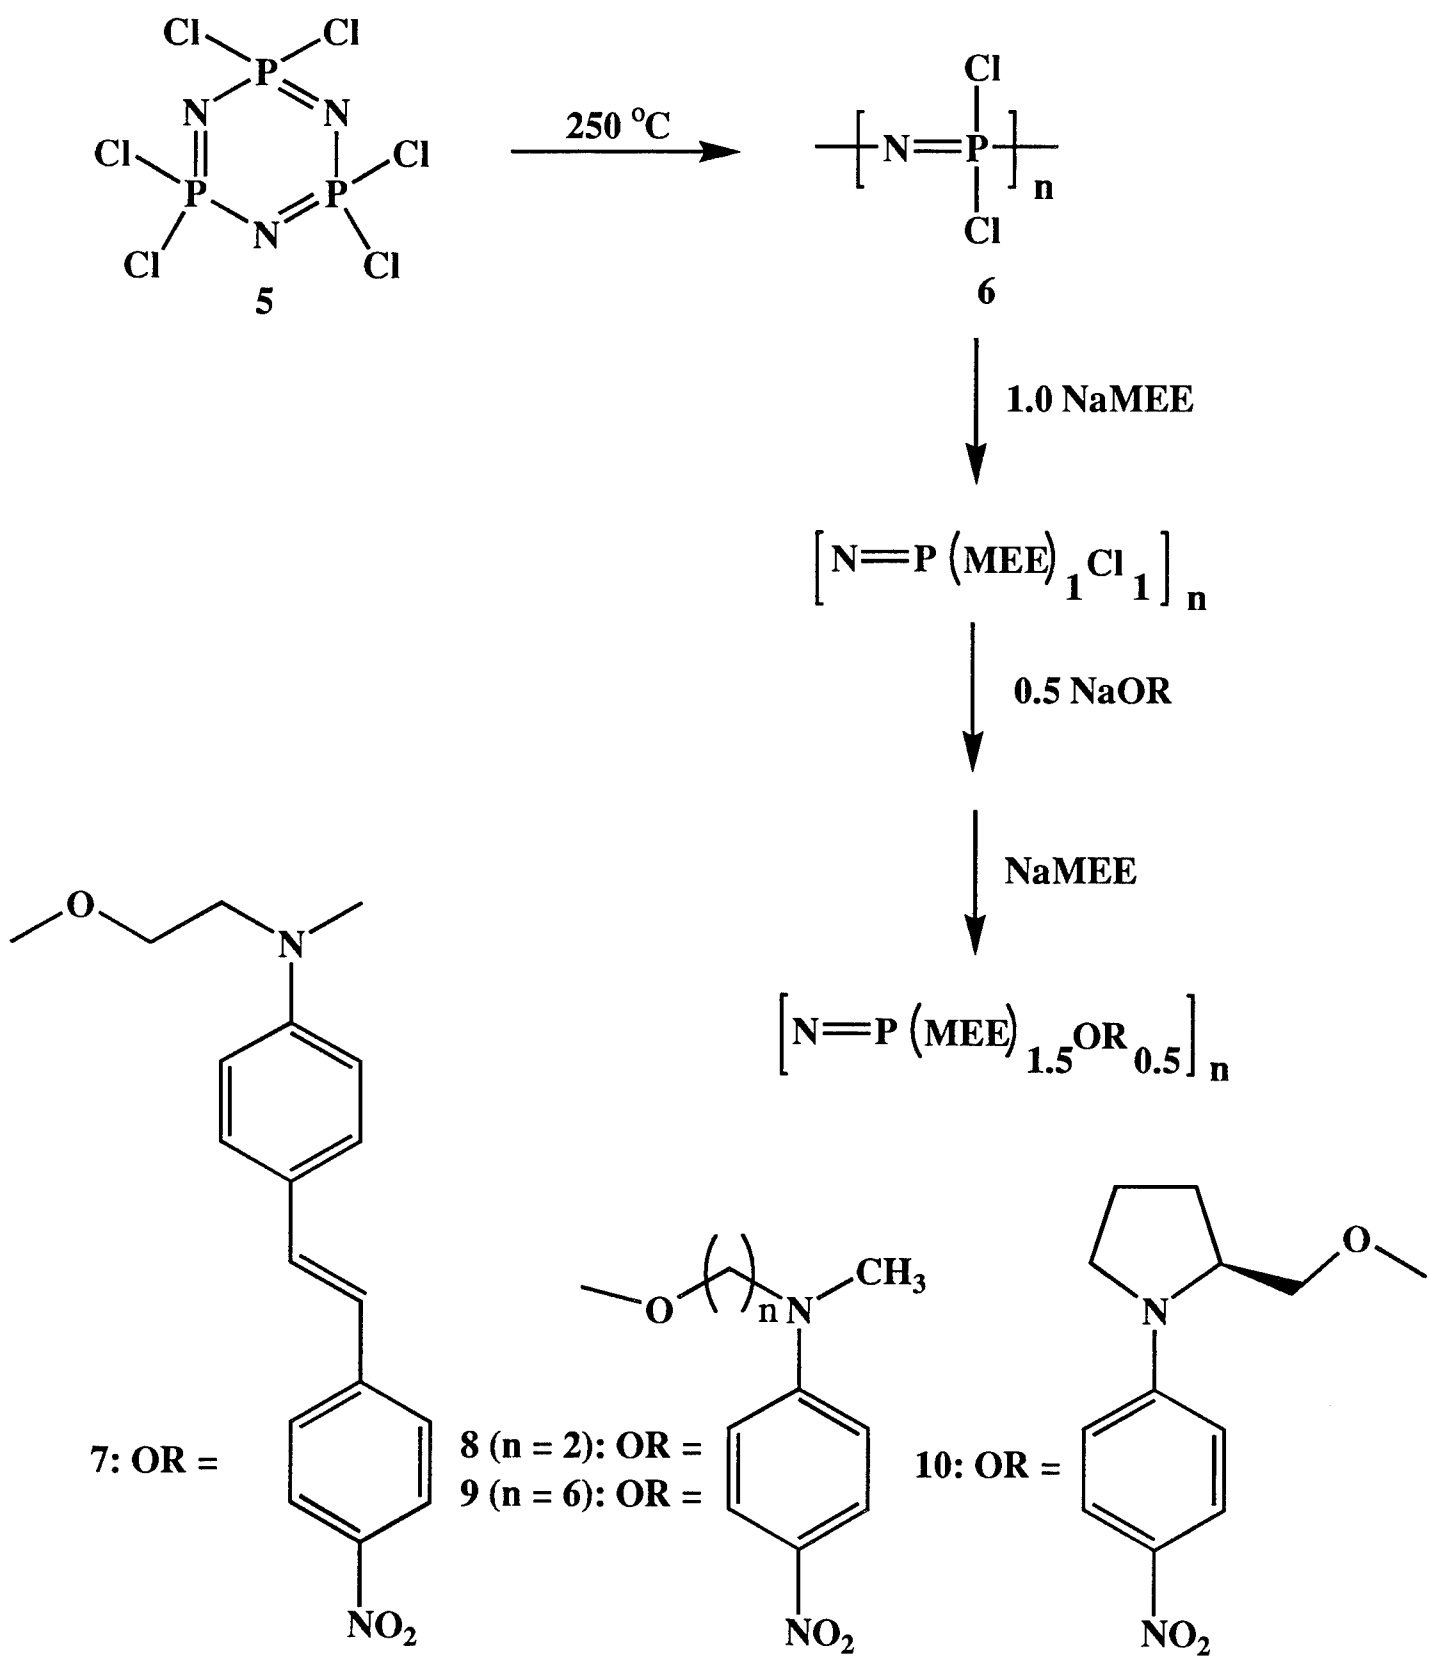

Scheme 2

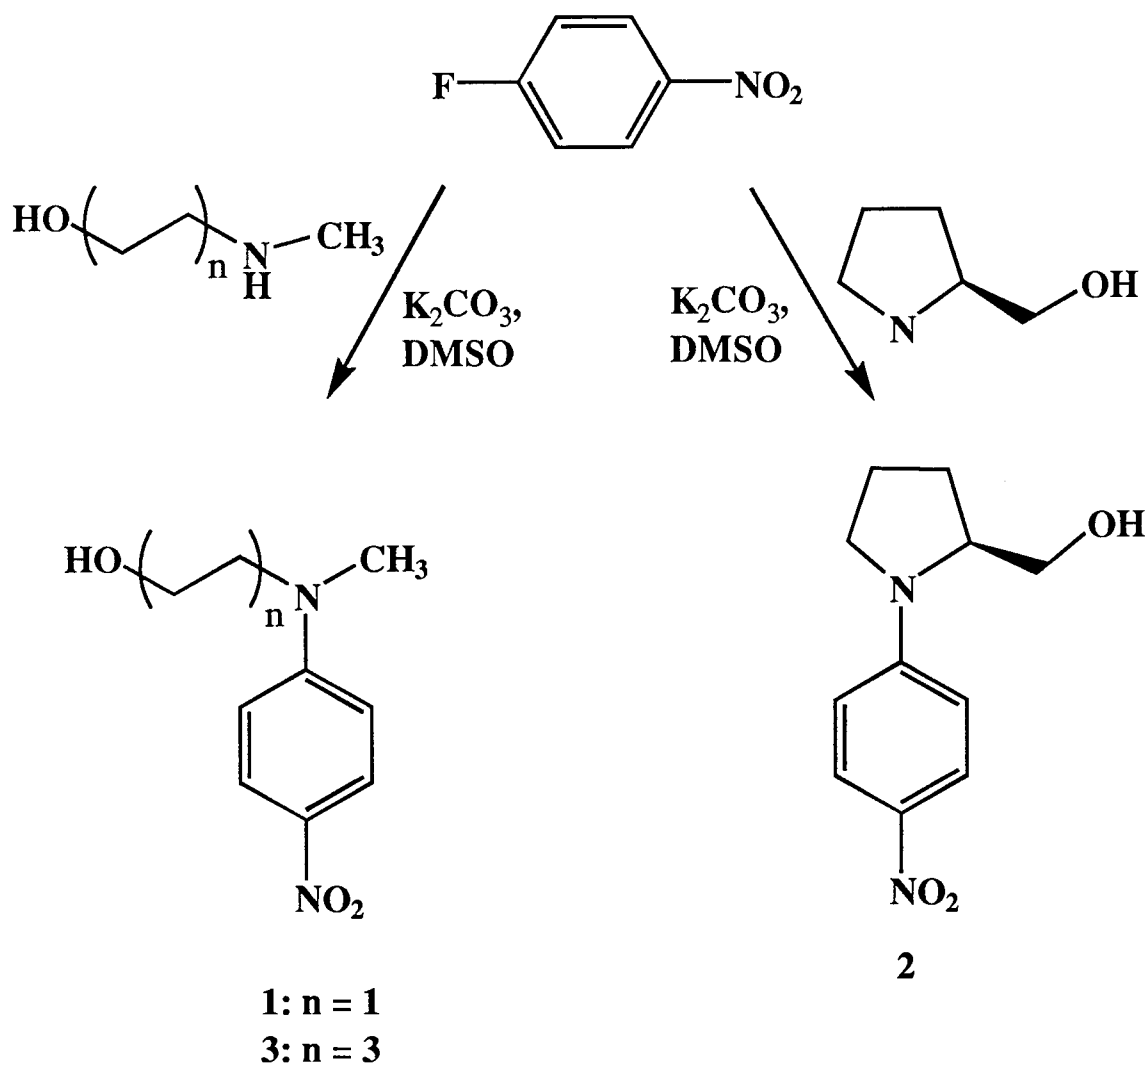

Scheme 3

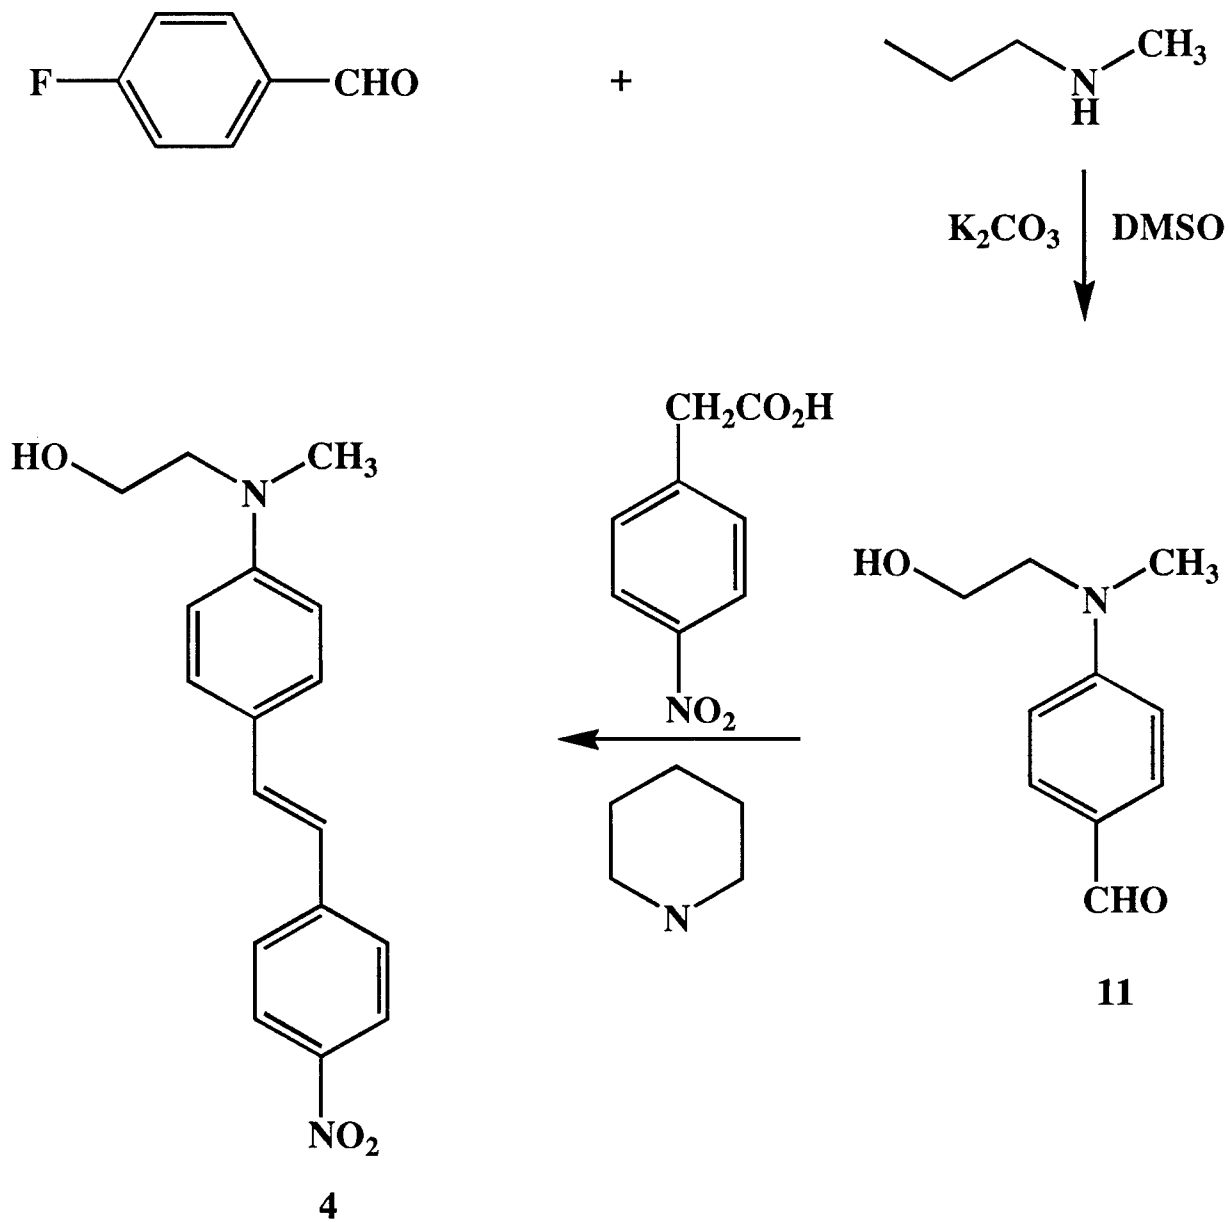

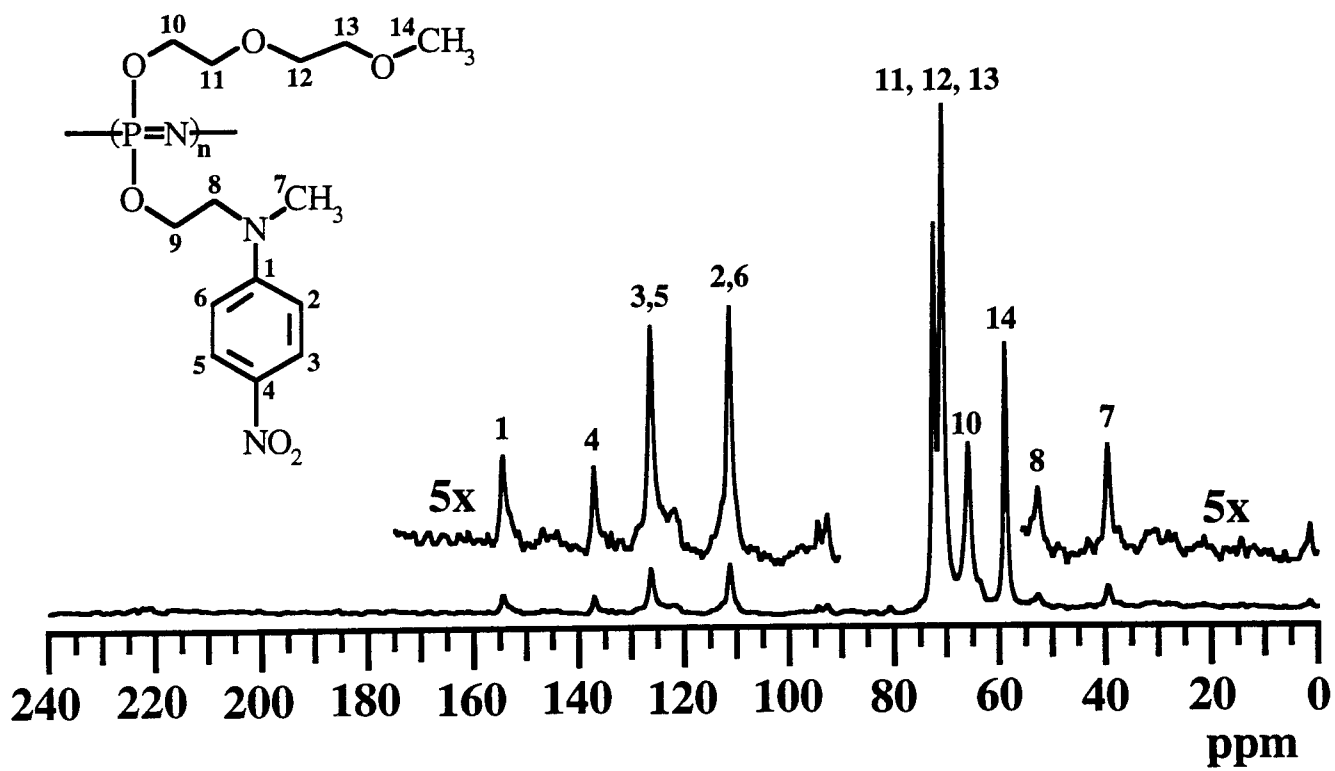
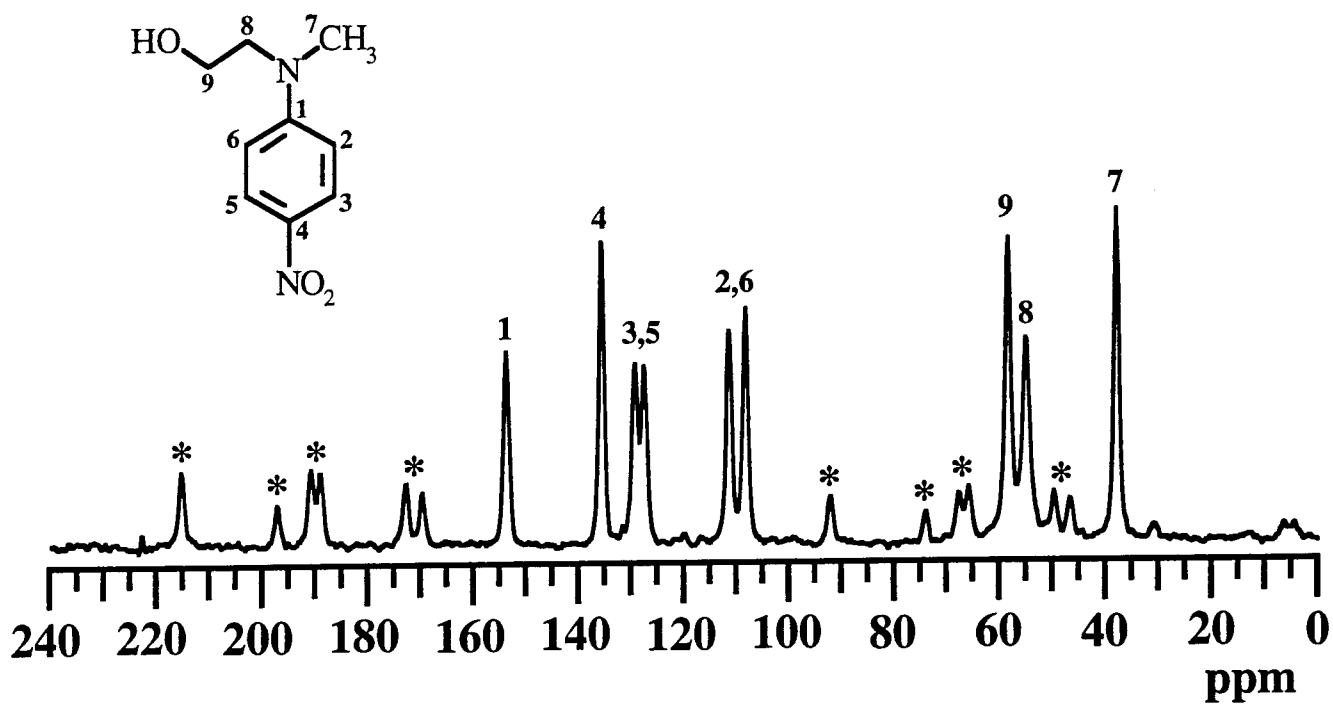


FIGURE 1

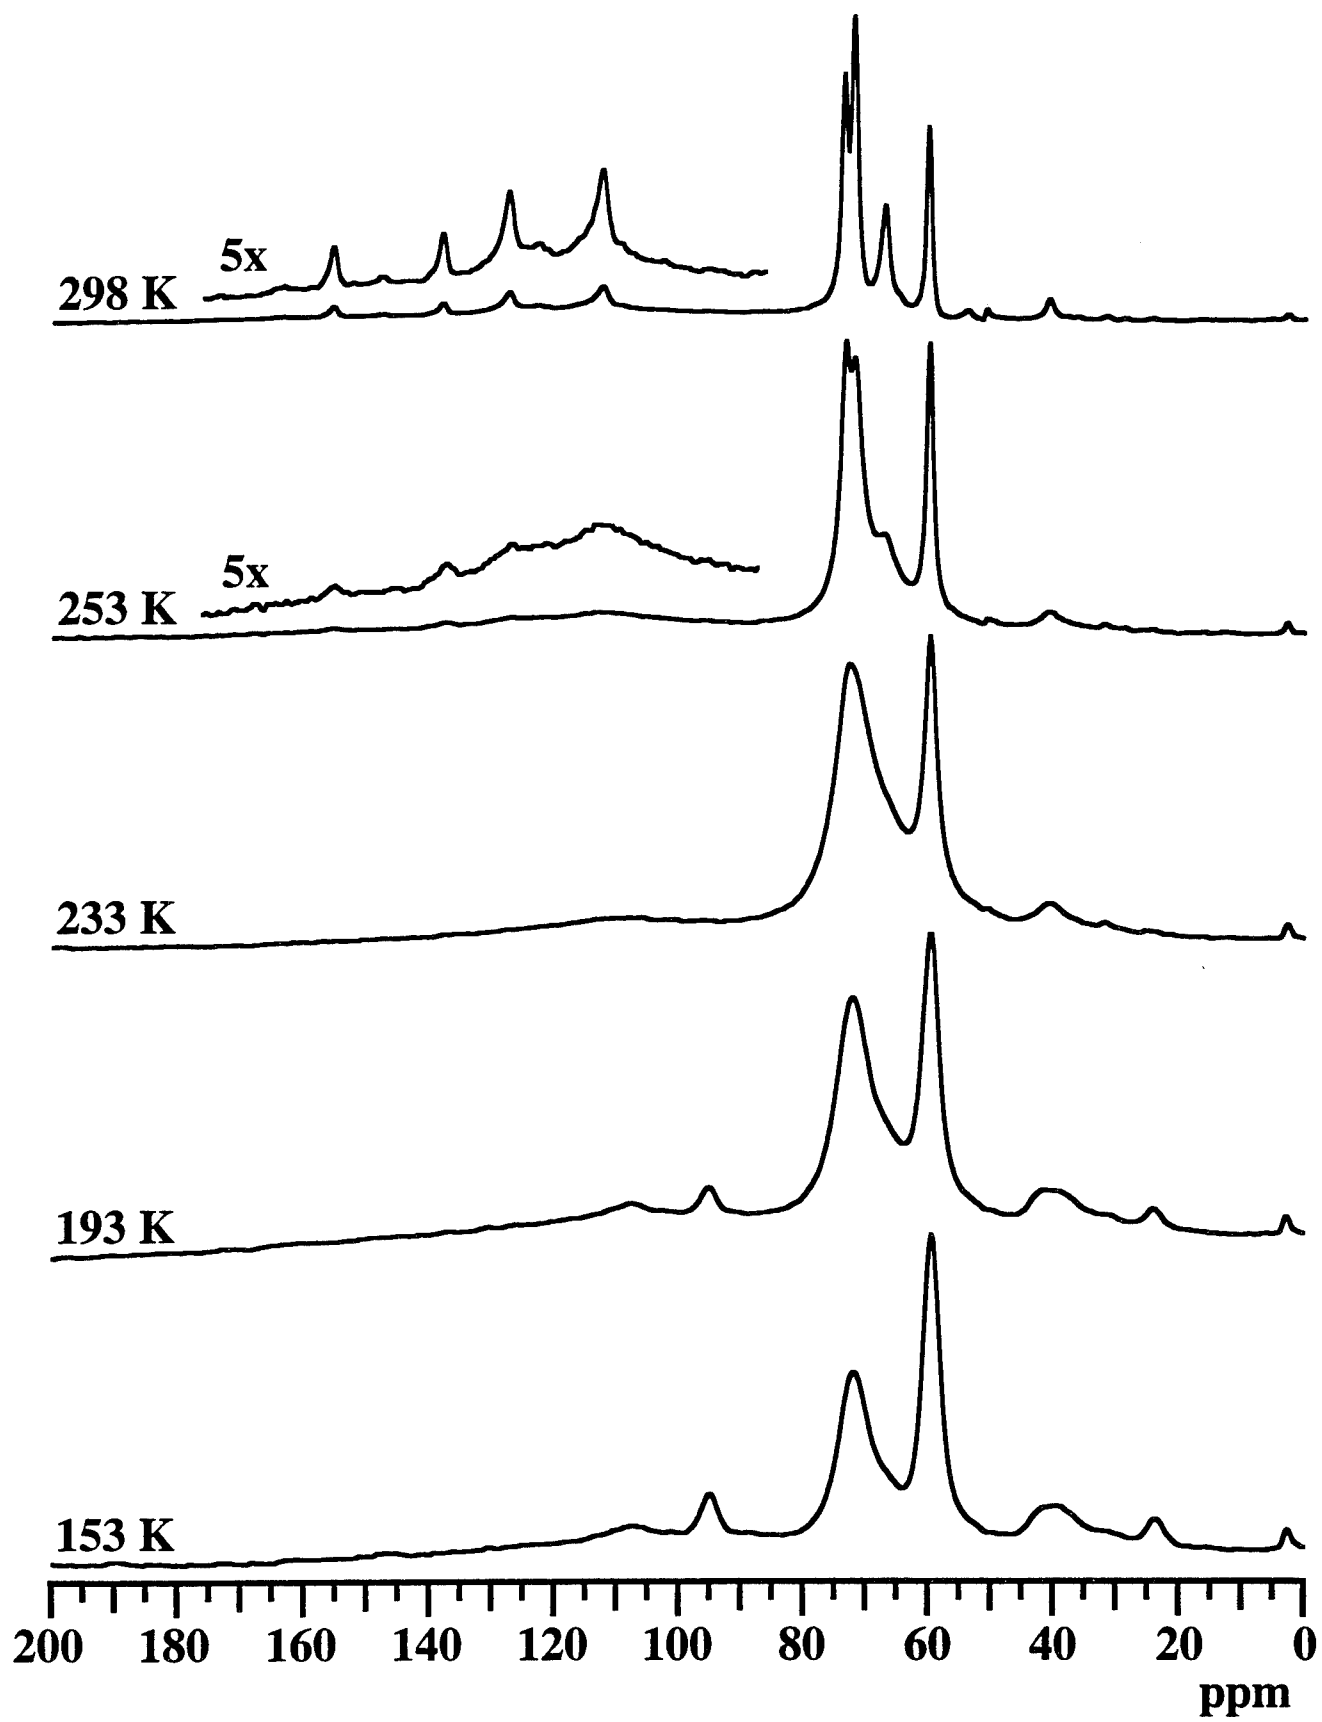


Figure 2

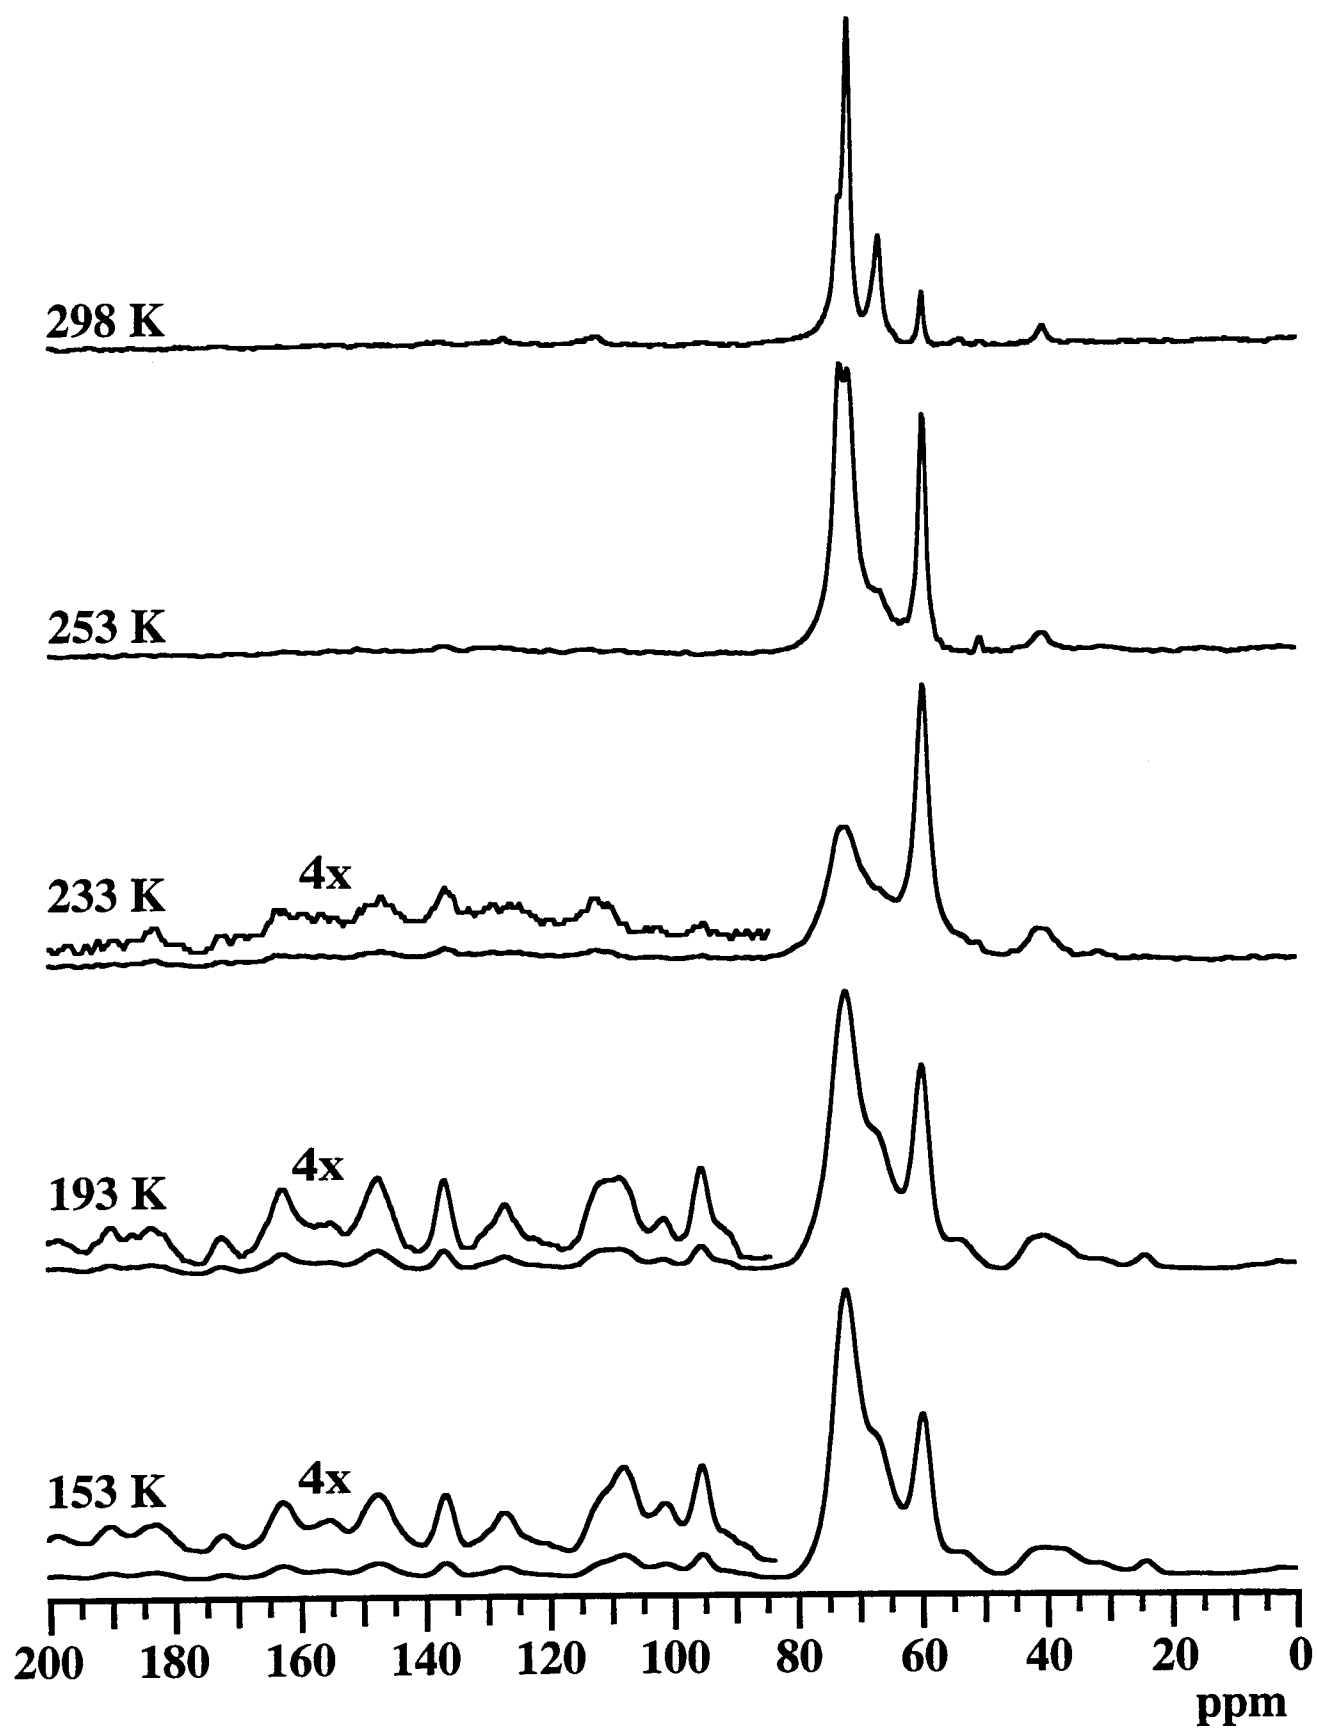


FIGURE 3

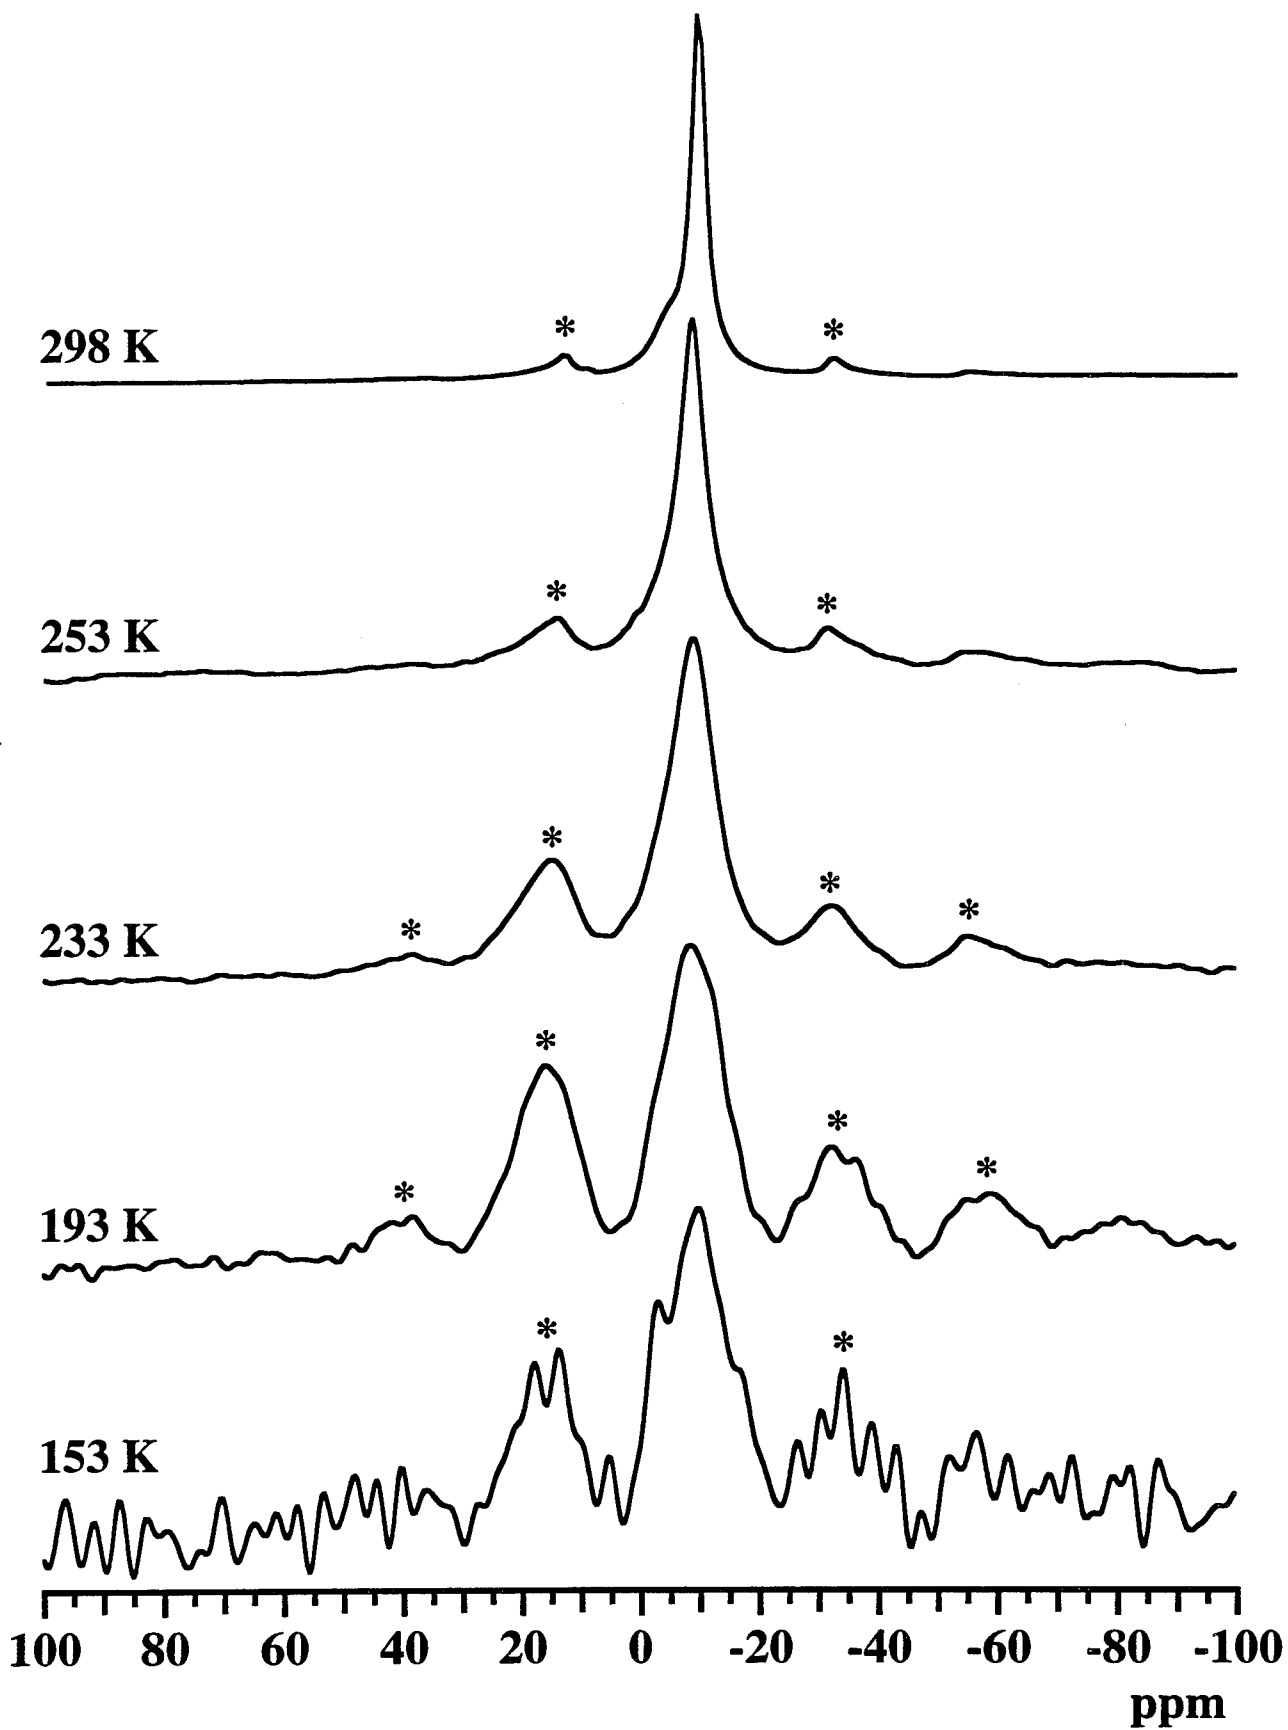


FIGURE 4

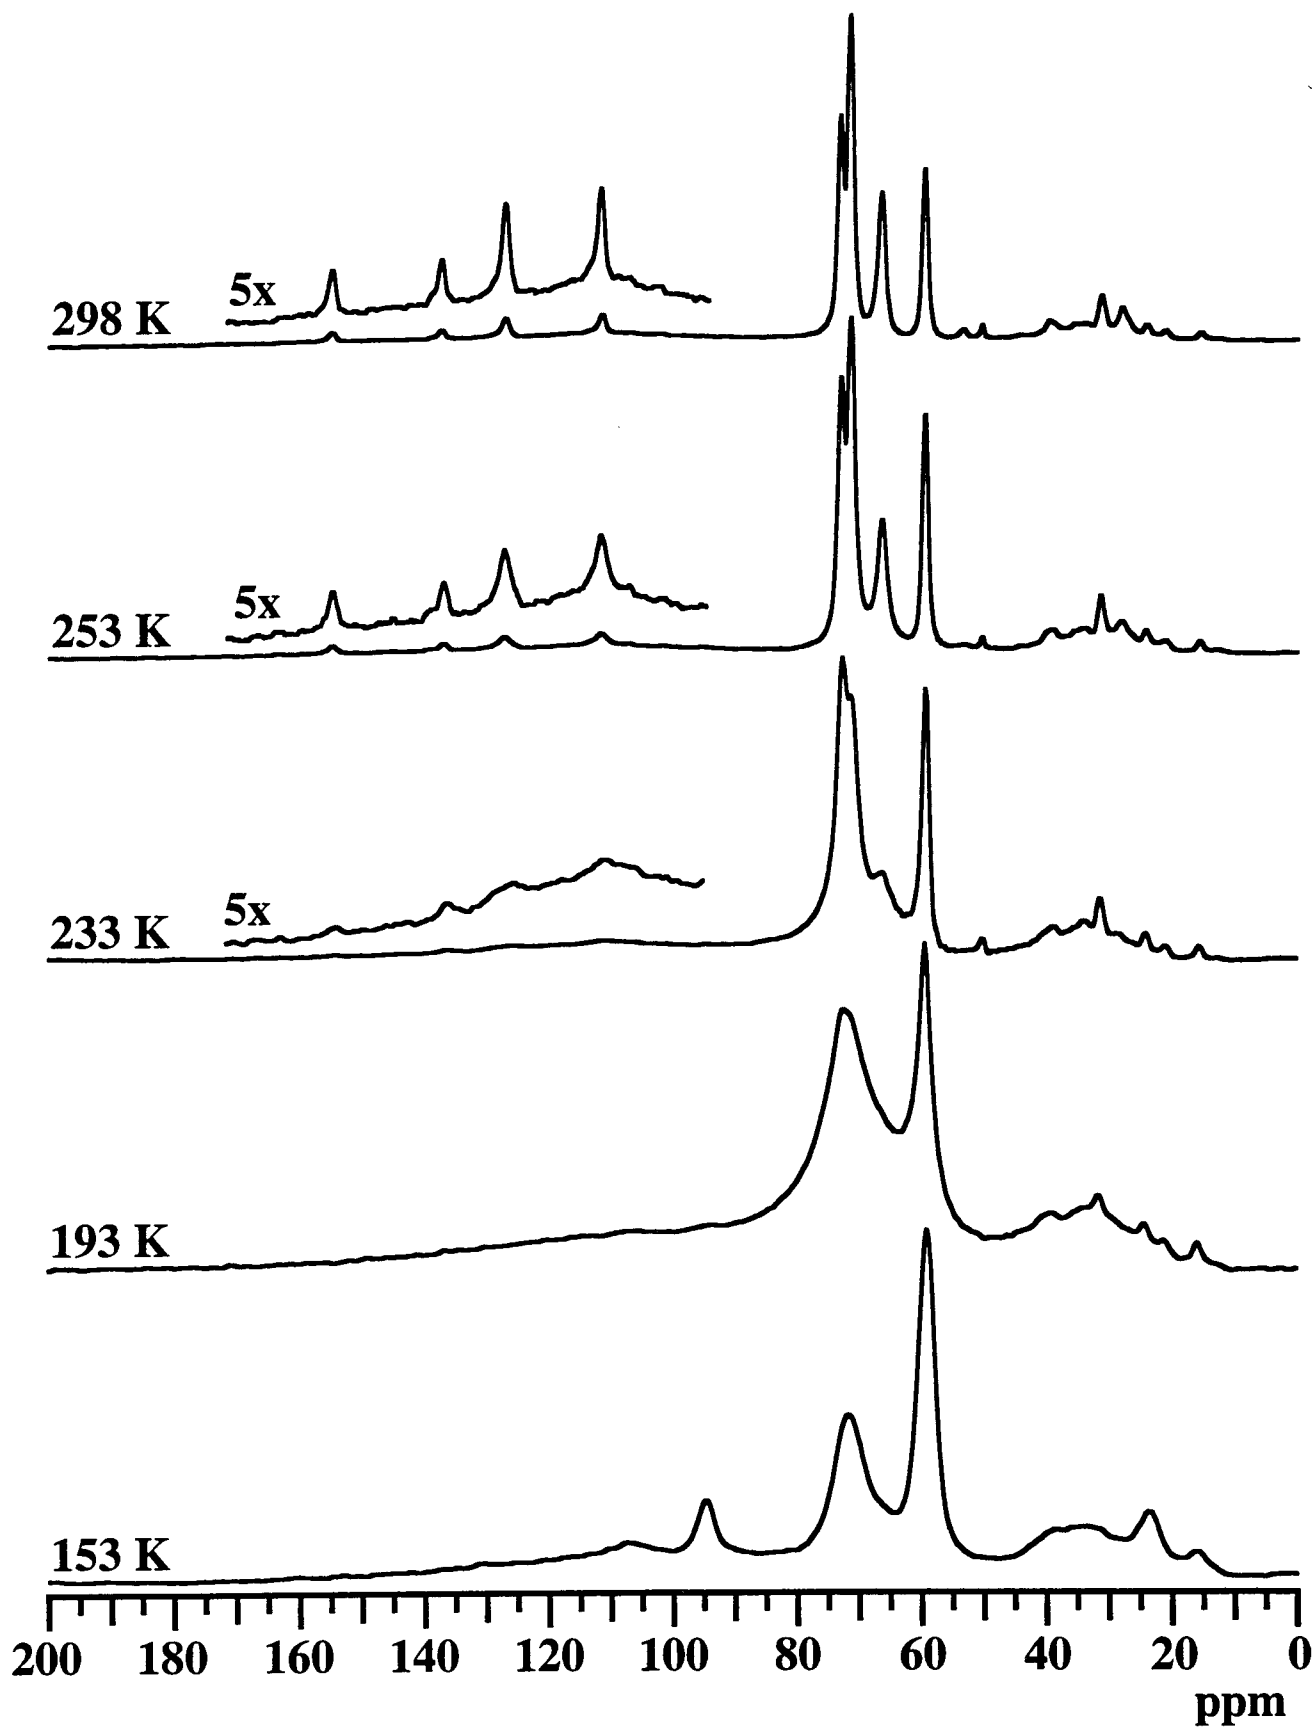


Figure 5

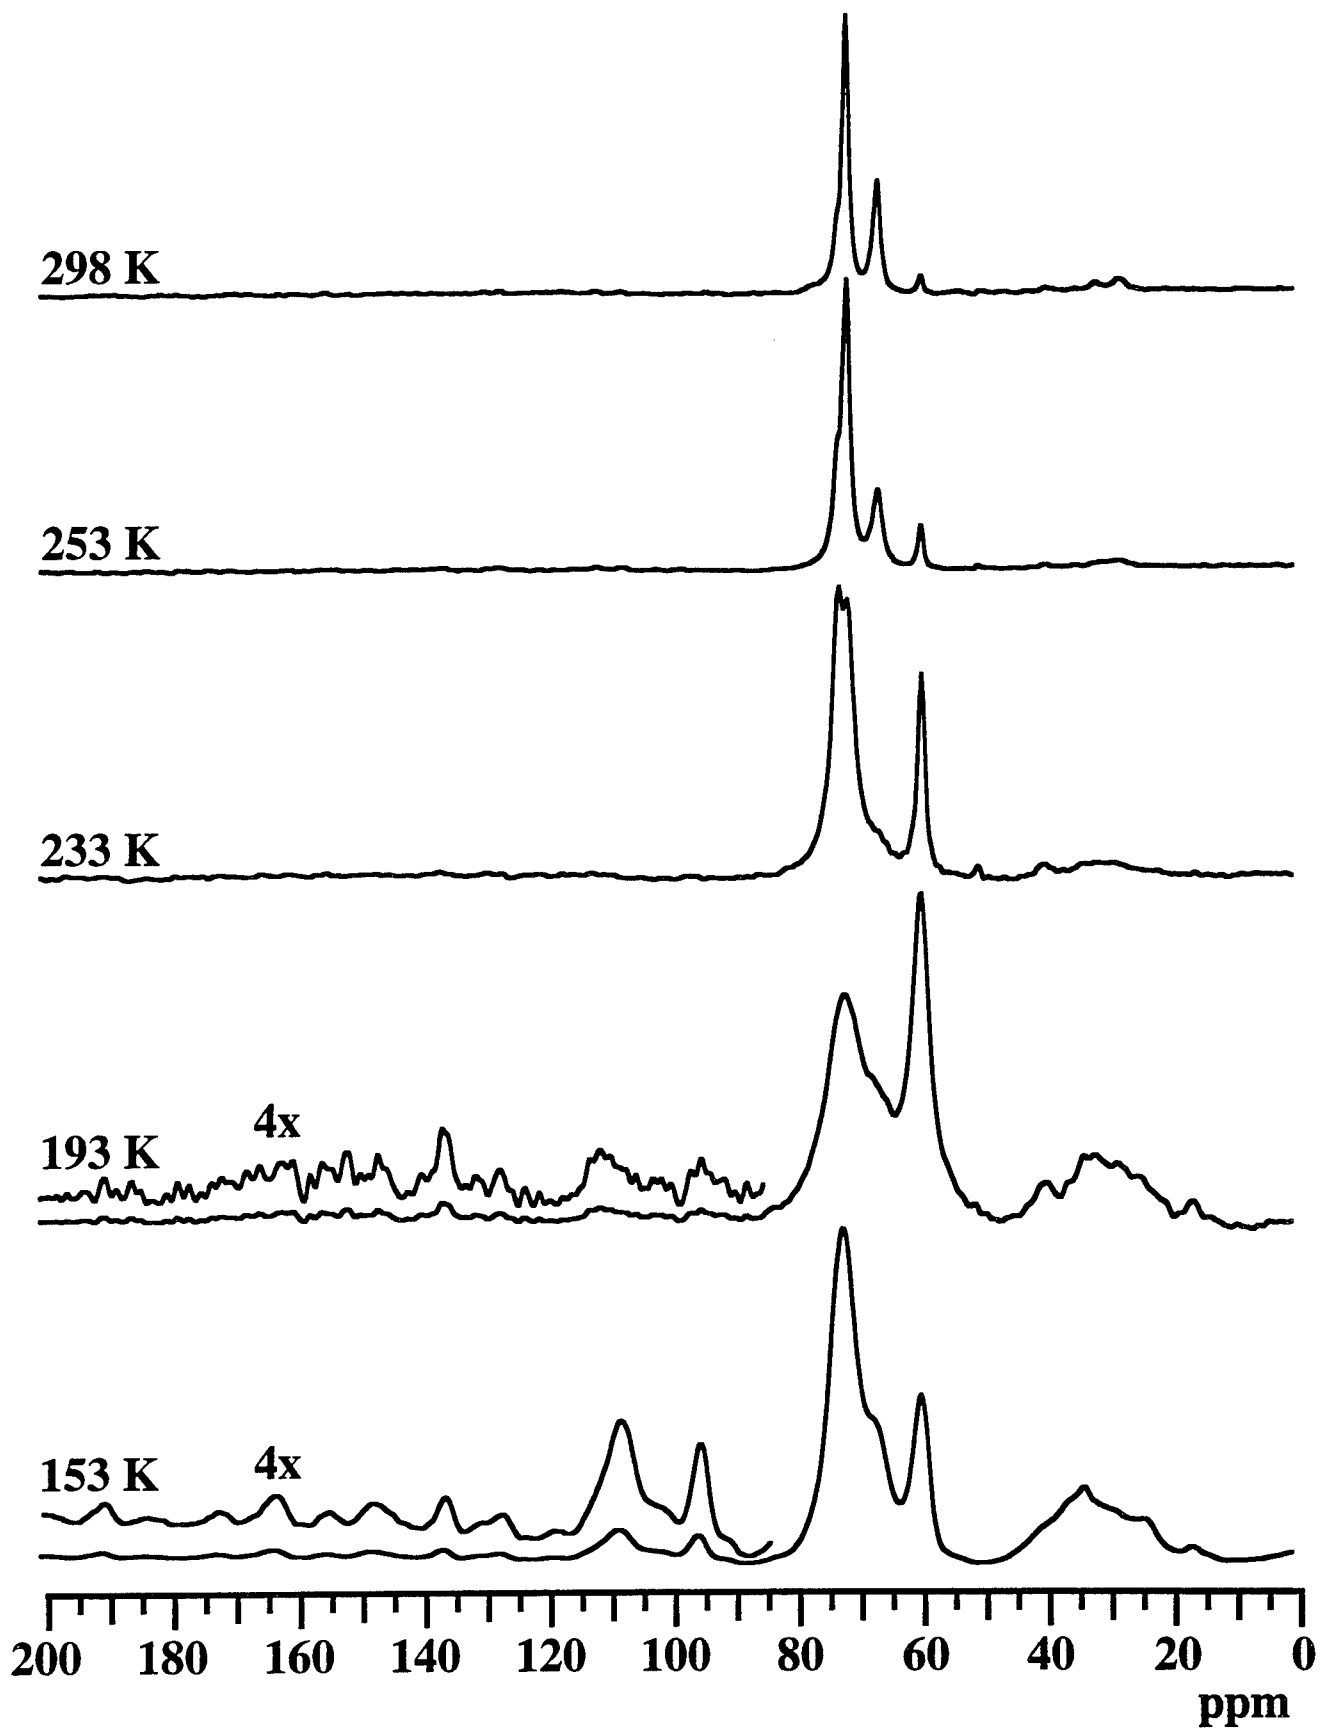


FIGURE 6

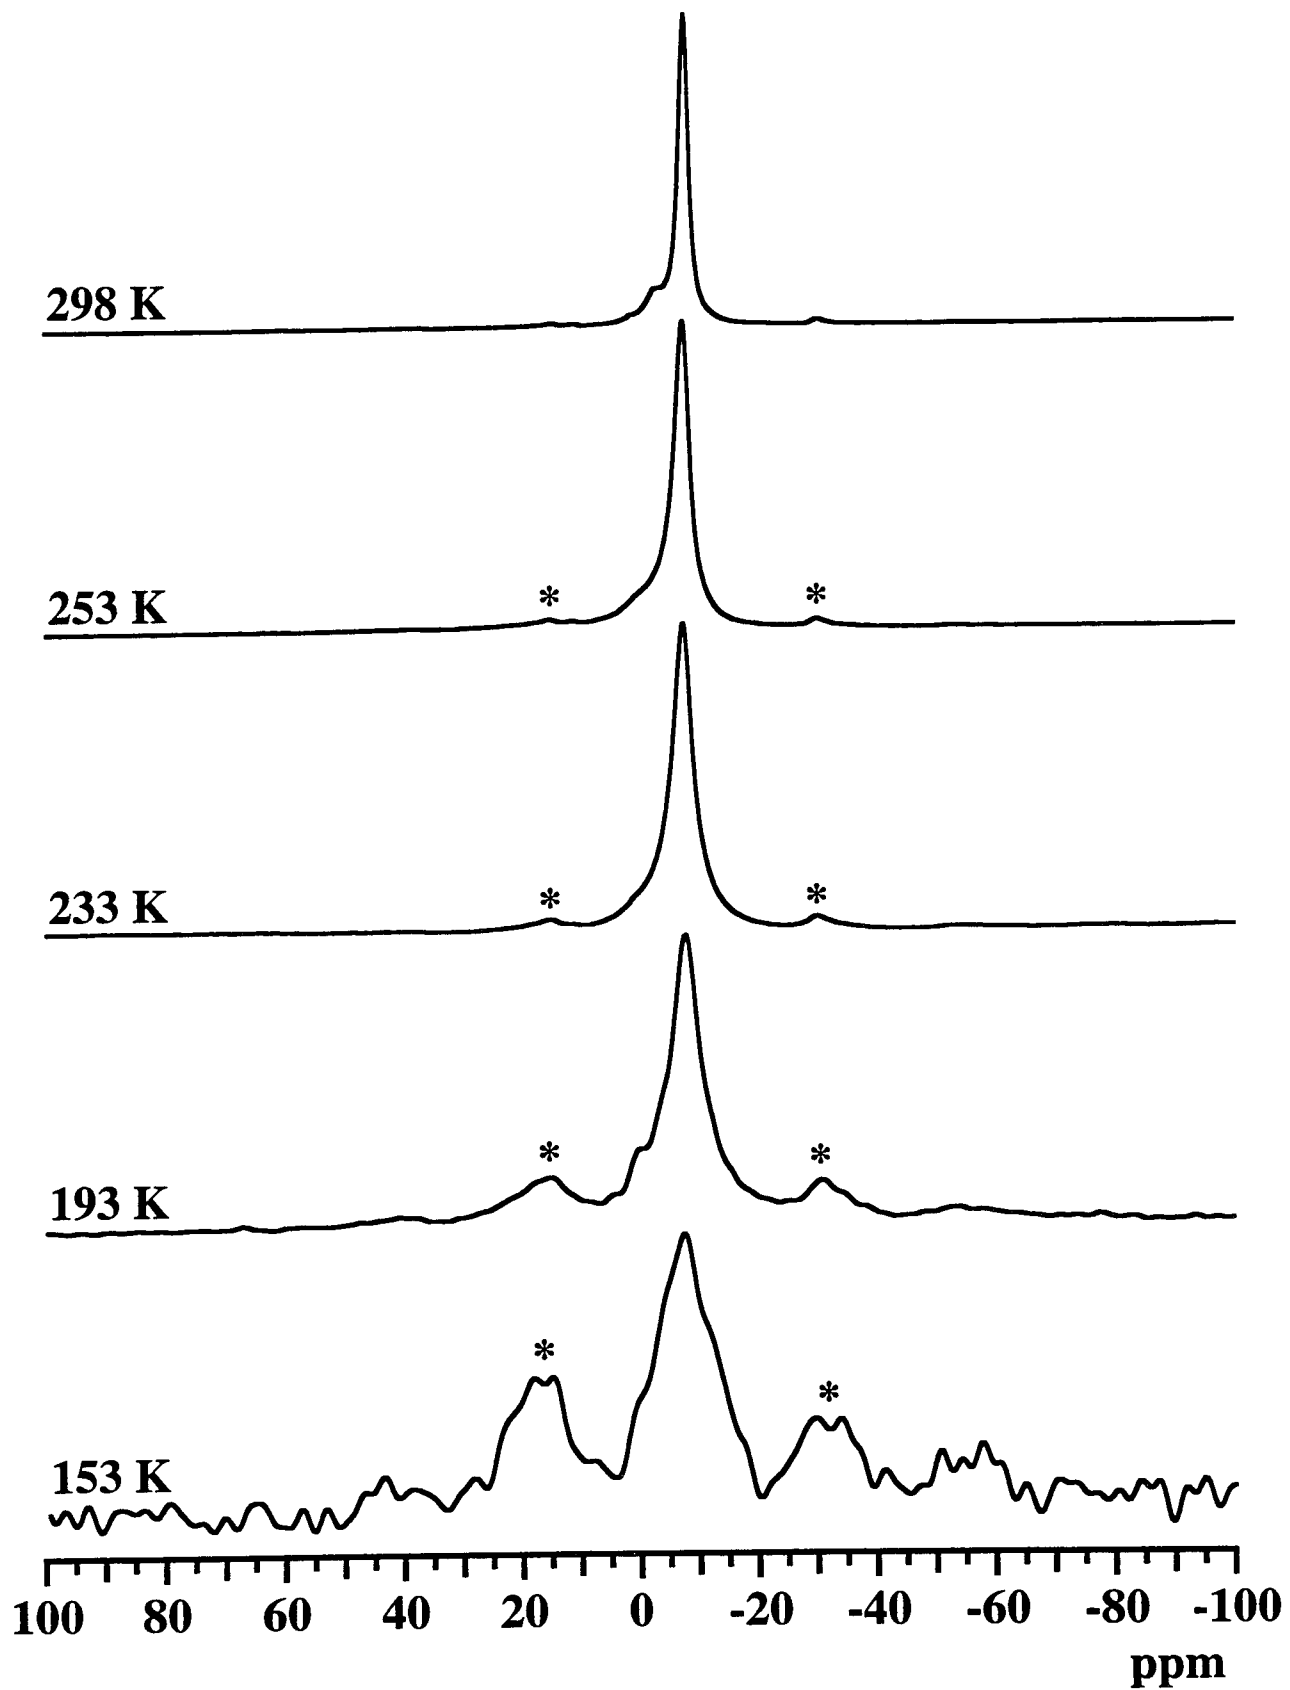


FIGURE 7

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research Chemistry Division, Code 313 800 North Quincy Street Arlington, Virginia 22217-5000	(1)*	Dr. Richard W. Drisko (1) Naval Civil Engineering Laboratory Code L52 Port Hueneme, CA 93043
Defense Technical Information Center Building 5, Cameron Station Alexandria, VA 22314	(2)	Dr. Harold H. Singerman (1) Naval Surface Warfare Center Carderock Division Detachment Annapolis, MD 21402-1198
Dr. James S. Murday Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	(1)	Dr. Eugene C. Fischer (1) Code 2840 Naval Surface Warfare Center Carderock Division Detachment Annapolis, MD 21402-1198
Dr. Robert Green, Director Chemistry Division, Code 385 Naval Air Weapons Center Weapons Division China Lake, CA 93555-6001	(1)	Dr. Bernard E. Douda (1) Crane Division Naval Surface Warfare Center Crane, Indiana 47522-5000
Dr. Elek Lindner Naval Command, Control and Ocean Surveillance Center RDT&E Division San Diego, CA 92152-5000	(1)	

* Number of copies to forward

DR. HARRY R. ALLCOCK
DEPARTMENT OF CHEMISTRY
PENNSYLVANIA STATE UNIV.
UNIVERSITY PARK, PA 16802

DR. ANDREW R. BARRON
DEPARTMENT OF CHEMISTRY
HARVARD UNIVERSITY
CAMBRIDGE, MA 02138

DR. KURT BAUM
FLUOROCEM, INC.
680 SOUTH AYON AVENUE
AZUSA, CA 91702

DR. FRANK D. BLUM
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF MISSOURI - ROLLA
ROLLA, MO 65401

DR. ALEXANDER S. BLUMSTEIN
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF MASSACHUSETTS
LOWELL, MA 01854

DR. LEONARD J. BUCKLEY
AIRCRAFT DIVISION, CODE 6064
NAVAL AIR WARFARE CENTER
P.O. BOX 5152
WARMINSTER PA 18974-0591

PROF. TOBY M. CHAPMAN
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF PITTSBURGH
PITTSBURGH PA 15261

DR. ROBERT E. COHEN
DEPARTMENT OF CHEMICAL ENGINEERING
MASSACHUSETTS INSTITUTE OF TECHNOLOGY
CAMBRIDGE, MA 02139

PROF. JOSEPH M. DESIMONE
DEPARTMENT OF CHEMISTRY
THE UNIVERSITY OF NORTH
CAROLINA AT CHAPEL HILL
CHAPEL HILL, NC 27599-3290

DR. RANDOLPH S. DURAN
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF FLORIDA
GAINESVILLE, FL 32611

DR. CURTIS W. FRANK
DEPARTMENT OF CHEMICAL ENGINEERING
STANFORD UNIVERSITY
STANFORD, CA 94305

DR. JEAN M. FRECHET
DEPARTMENT OF CHEMISTRY
CORNELL UNIVERSITY
ITHACA, NY 14853

DR. JOSEPH A. GARDELLA
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF BUFFALO
BUFFALO, NY 14214

DR. JAMES R. GRIFFITH
CODE 6120
DEPARTMENT OF THE NAVY
NAVAL RESEARCH LABORATORY
4555 OVERLOOK AVENUE, SW
WASHINGTON, DC 20375-5000

DR. ROBERT H. GRUBBS
DEPARTMENT OF CHEMISTRY
CALIFORNIA INST. OF TECHNOL.
PASADENA, CA 91124

DR. I. I. HARRUNA
DEPARTMENT OF CHEMISTRY
MORRIS BROWN COLLEGE
ATLANTA, GA 30314

DR. JAMES F. HAW
DEPARTMENT OF CHEMISTRY
TEXAS A&M UNIVERSITY
COLLEGE STATION, TX 77843

DR. ALAN J. HEEGER
DEPARTMENT OF PHYSICS
UNIV. OF CALIFORNIA
SANTA BARBARA, CA 93106

DR. HATSUO ISHIDA
DEPARTMENT OF MACROMOLECULAR SCIENCES
CASE WESTERN RESERVE UNIV.
CLEVELAND, OH 44106

DR. RICHARD B. KANER
DEPARTMENT OF CHEMISTRY & BIOCHEMISTRY
UNIVERSITY OF CALIFORNIA, LA
LOS ANGELES CA

DR. JOHN F. KEANA
UNIVERSITY OF OREGON
EUGENE, OR 97403

DR. JEFFREY T. KOBERSTEIN
INSTITUTE OF MATERIALS SCIENCE
UNIVERSITY OF CONNECTICUT
STORRS, CT 06268

PROF. HILARY S. LACKRITZ
DEPARTMENT OF CHEMICAL ENGINEERING
PURDUE UNIVERSITY
WEST LAFAYETTE IN 49707

PROF. RICHARD M. LAINE
DEPT. OF MATERIALS SCIENCE
AND ENGINEERING
THE UNIVERSITY OF MICHIGAN
H.H. DOW BUILDING
ANN ARBOR MI 48105-2137

DR. GEOFFREY LINDSAY
CHEMISTRY DIVISION - CODE 3858
NAVAL WEAPONS CENTER
CHINA LAKE, CA 93555

PROF. ALAN G. MACDIARMID
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF PENNSYLVANIA
CHEMISTRY BUILDING
PHILADELPHIA PA 19104-6323

DR. ASLAM MALIK
AEROJET PROPULSION DIVISION
P.O. BOX 13222
SACRAMENTO CA 95813-6000

DR. LON J. MATHIAS
DEPARTMENT OF POLYMER SCIENCE
UNIVERSITY OF SOUTHERN MISSISSIPPI
HATTIESBURG MS 39406-0076

DR. KRZYSZTOF MATYJASZEWSKI
DEPARTMENT OF CHEMISTRY
CARNEGIE-MELLON UNIVERSITY
PITTSBURGH, PA 15213

DR. ALON MCCORMICK
CHEMICAL ENGINEERING & MATERIALS
SCIENCES DEPARTMENT
UNIVERSITY OF MINNESOTA
MINNEAPOLIS, MN 55455

DR. JAMES E. MCGRATH
DEPARTMENT OF CHEMISTRY
VIRGINIA POLYTECHNIC INSTITUTE
BLACKSBURG, VA 24061

DR. JAMES A. MOORE
DEPARTMENT OF CHEMISTRY
RENSSELAER POLYTECHNIC INSTITUTE
TROY, NY 12180-3590

DR. GEORGE MUSHRUSH
DEPARTMENT OF CHEMISTRY
GEORGE MASON UNIVERSITY
FAIRFAX, VA 22030

DR. MICHAEL L. MYRICK
DEPARTMENT OF CHEMISTRY AND BIOCHEMISTRY
UNIVERSITY OF SOUTH CAROLINA
COLUMBIA SC 29208

PROF. A. NATANSOHN
QUEENS UNIVERSITY
KINGSTON ONTARIO
CANADA K7L 3N6

DR. DOUGLAS C. NECKERS
DEPARTMENT OF CHEMISTRY
BOWLING GREEN UNIVERSITY
BOWLING GREEN, OH 43403

DR. BRUCE M. NOVAK
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF CALIFORNIA
BERKELEY, CA 94720

DR. CHRISTOPHER K. OBER
MATERIALS SCIENCE & ENGINEERING
BARD HALL, CORNELL UNIVERSITY
ITHACA NY 14853-1501

DR. PETER N. PENTAURO
DEPARTMENT OF ELECTRICAL ENGINEERING
TULANE UNIVERSITY
314 GIBSON HALL
NEW ORLEANS LA 70118-5698

DR. VIRGIL PERCEC
DEPARTMENT OF MACROMOLECULAR SCIENCES
CASE WESTERN RESERVE UNIV.
CLEVELAND, OH 44106-2699

DR. MICHAEL F. RUBNER
MATERIALS SCIENCE & ENGINEERING
DEPARTMENT
MASSACHUSETTS INST. OF TECH.
CAMBRIDGE, MA 02139

DR. JACOB SCHAEFER
DEPARTMENT OF CHEMISTRY
WASHINGTON UNIVERSITY
ST. LOUIS, MO 63130

DR. JERRY I. SCHEINBEIM
DEPARTMENT OF MECHANICAL
& MATERIALS SCIENCES
RUTGERS UNIVERSITY
PISCATAWAY, NJ 08854

DR. RICHARD R. SCHROCK
DEPARTMENT OF CHEMISTRY, 6-331
MASSACHUSETTS INSTITUTE OF TECHNOLOGY
77 MASSACHUSETTS AVENUE
CAMBRIDGE, MA 02139

DR. R. SHASHIDHAR
CENTER FOR BIO/MOLECULAR SCIENCE & ENG.
NAVAL RESEARCH LABORATORY
CODE 60909
WASHINGTON DC 20375-5320

DR. ARTHUR W. SNOW
CHEMISTRY DIVISION
NAVAL RESEARCH LABORATORY
MATERIALS CHEMISTRY BRANCH
CODE 6120
WASHINGTON DC 20375

PROF. SAMUEL I. STUPP
DEPT OF MATERIALS SCIENCE & ENGINEERING
UNIVERSITY OF ILLINOIS AT URBANA-CHAMPAIGN
1304 WEST GREEN STREET
URBANA, IL 61801

DR. C. S. SUNG
INSTITUTE OF MATERIALS SCIENCE
UNIVERSITY OF CONNECTICUT
STORRS, CT 06268

DR. JAMES M. TOUR
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF SOUTH CAROLINA
COLUMBIA, SC 29208

PROF. S. K. TRIPATHY
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF LOWELL
LOWELL, MA 01854

DR. DAVID M. WALBA
DEPARTMENT OF CHEMISTRY & BIOCHEMISTRY
UNIVERSITY OF COLORADO
BOULDER, CO 80309

DR. C. H. WANG
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF NEBRASKA
LINCOLN, NE 68588-0304

DR. ROBERT WEST
DEPARTMENT OF CHEMISTRY
UNIVERSITY OF WISCONSIN-MADISON
MADISON WI 53706

DR. MICHAEL E. WRIGHT
DEPARTMENT OF CHEMISTRY
UTAH STATE UNIVERSITY
LOGAN, UT 84322

DR. LUPING YU
DEPARTMENT OF CHEMISTRY
THE UNIVERSITY OF CHICAGO
970 E. 58TH STREET
CHICAGO IL 60637