

3627

**REPORT DOCUMENTATION PAGE**

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments and suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Services, Washington, DC 20540-6000, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave Blank)		2. REPORT DATE September 1995	3. REPORT TYPE AND DATES COVERED Final 04/01/92—04/30/95	
4. TITLE AND SUBTITLE Transformation Toughening of Ceramics			5. FUNDING NUMBERS 61102F 2306 BS F49620- 92-C-0028	
4. AUTHOR(S) D.B. Marshall			7. PERFORMING ORGANIZATION REPORT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) ROCKWELL INTERNATIONAL SCIENCE CENTER 1049 CAMINO DOS RIOS THOUSAND OAKS, CA 91360			7. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) AFOSR/ME Building 410 Bolling AFB, DC 20332-6448			9. SPONSORING / MONITORING AGENCY REPORT NUMBER F49620-92-C-0028	
11. SUPPLEMENTARY NOTES			19951011 026	
12a. DISTRIBUTING/AVAILABILITY STATEMENT APPROVED FOR PUBLIC RELEASE; DISTRIBUTION IS UNLIMITED			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 Words) This report summarizes the results from a 3-year research program aimed at developing a basic understanding of the microstructural design, fabrication, and properties of multilayered zirconia-based composites with high toughness and oxidation resistance. Most of the effort focused on multilayered composites of Ce-ZrO <sub>2</sub> and Al <sub>2</sub> O <sub>3</sub> which have strongly bonded interfaces. The design of the layered composite microstructure was based on micromechanics analysis: the layers modify the shape and extent of a crack tip transformation zone, leading to toughnesses over 20 MPa.m <sup>1/2</sup> . Optimum layer thicknesses were determined and related to effects of autocatalytic transformation and crack tip advance mechanisms. Crack resistance curves were measured at various temperatures: the very high toughnesses (> 10 MPa.m <sup>1/2</sup> ) were limited to temperature range of ~ 100°C above the Ms temperature for the martensitic transformation. A preliminary study of multilayered composites containing weakly bonded layers (which achieve toughening by debonding) indicated that rare earth phosphates (LaPO <sub>4</sub> and CePO <sub>4</sub> ) are potentially suitable layers for Y- and Ce-stabilized zirconia composites.  DTIC QUALITY INSPECTED 5				
14. SUBJECT TERMS			15. NUMBER OF PAGES 16	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

**Table of Contents**

	<b>Page</b>
<b>1.0 Completed Project Summary .....</b>	<b>1</b>
Publications .....	1
Patent.....	3
Abstract of Objectives and Accomplishments .....	3
<b>2.0 Summary of Research .....</b>	<b>6</b>
2.1 Crack Resistance Curves in Layered Ce-ZrO <sub>2</sub> /Al <sub>2</sub> O <sub>3</sub> Ceramics .....	6
2.2 Mechanisms of Toughness Enhance in Zirconia-Based Laminar Composites .....	7
2.3 Transformation Mechanisms and Optimum Layer Thickness in Multilayered Zirconia Composites.....	8
2.4 Crack Growth Mechanisms in Laminar Zirconia Composites.....	10
2.5 Temperature Dependence of Toughening in Layered Zirconia Composites .....	11
2.6 Hardness-Size Effects and Residual Stresses in Multilayered ZrO <sub>2</sub> /Al <sub>2</sub> O <sub>3</sub> Composites .....	12
2.7 Indentation Studies of Y <sub>2</sub> O <sub>3</sub> -Stabilized ZrO <sub>2</sub> .....	13
2.8 Damage Accumulation and Cyclic Fatigue in Mg-PSZ at Hertzian Contacts .....	13
2.9 Debonding in Multilayered Composites of Zirconia and LaPO <sub>4</sub> .....	14
2.10 Fatigue Crack Growth and Stress Redistribution at Interfaces .....	15
<b>3.0 Transition of Accomplishments to Industry .....</b>	<b>16</b>

**List of Figures**

Figure		Page
1	Shear stress concentration adjacent to nontransforming layer ahead of crack tip in transformation toughened zirconia.....	8
2	Nomarski interference micrograph showing transformation zone in multilayered Ce-ZrO <sub>2</sub> /Al <sub>2</sub> O <sub>3</sub> composite: note more extensive transformation in narrower ZrO <sub>2</sub> layers (~30 μm thickness) and banded structure in wider layers. ....	9
3	Failure map showing transition in crack tip advance mechanism (which also defines the maximum toughness achievable). ....	10
4	Temperature dependence of toughening in multilayered Ce-ZrO <sub>2</sub> /Al <sub>2</sub> O <sub>3</sub> composite: (a) Crack resistance curves measured at various temperatures. (b) – (d) Nomarski interference micrographs showing transformation zones from specimens in (a). ....	12
5.	Broken beam of multilayered Ce-ZrO <sub>2</sub> /LaPO <sub>4</sub> , showing delamination at LaPO <sub>4</sub> layers. ....	14

Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification _____	
By _____	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

**1.0 Completed Project Summary**

**Title:** Transformation Toughening of Ceramics

**Principal Investigator:** Dr. D.B. Marshall

**Inclusive Dates:** April 1, 1992 through March 31, 1995

**Contract Number:** F49620-92-C-0028

**Senior Research Personnel:** Dr. D.B. Marshall, Dr. P.E.D. Morgan, Dr. R.M. Housley, Dr. M. Dadkhah and Dr. D.R. Mumm.

**Junior Research Personnel:** Dr. M.C. Shaw (while working on this project was employed at Rockwell and was also a part-time graduate student at the University of California, Santa Barbara; graduated 1994), Mr. E. Wright, Mr. J.J. Ratto, Ms. A. Taylor, Mr. E. Grethel and Ms. J. Dever (the last three were students under the Rockwell Youth Motivation Program).

**Publications:**

1. "Recovery of Crack Tip Transformation Zones in Zirconia after High Temperature Annealing," M.C. Shaw, D.B. Marshall, A.H. Heuer and E. Inghels, *J. Am. Ceram. Soc.*, **75**[2] 474-476 (1992).
2. "The Design of High Toughness Laminar Zirconia Composites," D.B. Marshall, *Bull. Am. Ceram. Soc.*, **71**[6] 969-973 (1992).
3. "Transformation Zone Shape Effects on Crack Shielding in Ceria-Partially-Stabilized Zirconia (Ce-TZP)-Alumina Composites," C.-S. Yu, D. Shetty, M.C. Shaw and D B. Marshall, *J. Am. Ceram. Soc.*, **75**[11] 2991-2994 (1992).

4. "Indentation Studies on  $Y_2O_3$ -Stabilized  $ZrO_2$ : I Development of Indentation-Induced Cracks," M.S. Kaliszewski, G. Behrens, et al., *J. Am. Ceram. Soc.*, **77**[5] 1185–1193 (1994).
5. "Crack Resistance Curves in Layered  $Ce-ZrO_2/Al_2O_3$  Ceramics," D.B. Marshall and J.J. Ratto, pp 517–523 in *Science and Technology of Zirconia V*. Eds S.P.S. Badwal, M.J. Bannister and R.J.H. Hannink, Technomic Pub. Co., 1993.
6. "Fatigue Crack Growth and Stress Redistribution at Interfaces," M.C. Shaw, D.B. Marshall, B.J. Dalgleish, M.S. Dadkhah and A.G. Evans, *Acta Met.*, **42**[12] 4091–4099 (1994).
7. "Debonding in Multilayered Composites of Zirconia and  $LaPO_4$ ," D.B. Marshall and P.E.D. Morgan, *J. Amer. Ceram. Soc.*
8. "Damage Accumulation and Cyclic Fatigue in Mg-PSZ at Hertzian Contacts," A. Pajares, L. Wei, B.R. Lawn and D.B. Marshall, *J. Mat. Res.*, (submitted).
9. "Temperature Dependence of Toughening in Layered Zirconia Composites," M.C. Shaw, D.R. Mumm and D.B. Marshall, for *J. Am. Ceram. Soc.*
10. "Crack Growth Mechanisms in Laminar Zirconia Composites," D.B. Marshall, for *J. Am. Ceram. Soc.*
11. "Mechanisms of Toughness Enhancement in Zirconia-Based Laminar Composites," D.B. Marshall, M.C. Shaw and D.R. Mumm, for *J. Am. Ceram Soc.*
12. "Hardness-Size Effects in Multilayered  $Al_2O_3/ZrO_2$  Composites," D.R. Mumm and D.B. Marshall for *J. Am. Ceram Soc.*
13. "Residual Stresses in Laminar  $Al_2O_3/ZrO_2$  Composites," D.B. Marshall, for *J. Am. Ceram. Soc.*

**Patent:**

“Partially Stabilized ZrO<sub>2</sub>-based Laminar Ceramic Composites,” D.B. Marshall, J.J. Ratto and F.F. Lange, U.S. Patent No. 5,284,698 (1994).

**Abstract of Objectives and Accomplishments**

The overall goal of this research was to generate a basic scientific understanding needed to develop high-toughness, oxidation-resistant composites based on zirconia. The specific objectives were: (1) to develop an understanding of factors that dictate the toughening of multilayered zirconia-based composites; (2) to provide a background of theoretical modeling and critical micromechanical measurements that will allow design of optimum microstructures as new material systems emerge; and (3) to develop the fabrication techniques needed to produce novel microstructures suggested by the theoretical modeling.

A major part of the research involved studies of layered composites of alumina and zirconia. In these composites, which were designed from predictions of our micromechanics modeling of transformation toughening in zirconia, the role of the alumina layers is to interrupt the autocatalytic transformation, and beneficially modify the shape of the crack-tip transformation zone. This toughening mechanism has resulted in toughnesses over 20 MPa.m<sup>1/2</sup> in multilayered Ce-ZrO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> composites. Measurements and observations from in situ mechanical testing and Raman spectroscopy, using a range of composites that were fabricated with controlled variations of microstructure, yielded the following main conclusions: (1) the optimum layer thicknesses are between about 5 and 20 times the grain size (~ 15 and 60 μm for transformable Ce-ZrO<sub>2</sub>); (2) the peak toughness can be limited by defects in the nontransforming layer via a transition in crack tip growth mechanism (a map defining this transition was developed); (3) the very high toughnesses (> 10 MPa.m<sup>1/2</sup>) are limited to a relatively narrow temperature range, within ~ 100°C above the temperature at which spontaneous martensitic transformation occurs.

An alternative approach for toughening brittle composites is to introduce interfaces or layers that debond when intercepted by a crack (interfaces in the Al<sub>2</sub>O<sub>3</sub>/ZrO<sub>2</sub> layered composites are strong and showed no evidence of debonding). Following our discovery in another program that LaPO<sub>4</sub> forms a weak interface with Al<sub>2</sub>O<sub>3</sub>, we explored the bonding and stability of LaPO<sub>4</sub>

with several  $ZrO_2$  systems, with the possibility in mind of combining toughening due to transformation and debonding. Multilayered composites were fabricated with alternating layers of  $LaPO_4$  and  $ZrO_2$  that was partially stabilized with either  $CeO_2$  or  $Y_2O_3$ , or with 2-phase  $Al_2O_3$ - $ZrO_2$  layers. Debonding and distributed damage were observed in all cases. The  $LaPO_4$  and  $Y_2O_3$ -stabilized  $ZrO_2$  layers were stable in air, with no interdiffusion detected at temperatures up to  $1600^\circ C$ . However, in the  $CeO_2$ -stabilized system, interdiffusion of Ce and La occurred, leading to formation of (Ce, La) magnetoplumbites. The results suggest that  $CePO_4$  may be a better interlayer for  $CeO_2$ -stabilized zirconia.

The role of the interface in redistributing stress around cracks in multilayered composites with alternating brittle and ductile components was investigated. The validity of models for the role of debonding and slip on stress redistribution was examined by comparing predictions with stresses measured by fluorescence spectroscopy. Debonding was substantially more effective than slip at reducing the stress. Under fatigue loading of these composites, two competing mechanisms were observed: mixed mode cracks extended along the metal/ceramic interfaces normal to the tip of the main crack (thus reducing the stresses ahead of the crack); while intact metal ligaments bridging the crack ruptured rapidly by Mode I fatigue crack growth (thus increasing the crack tip stress). This duality in fatigue behavior might be exploited to optimize the fatigue resistance of metal ceramic multilayers.

Substantial effort was also devoted to improving fabrication methods for the multilayered ceramic composites developed under this program. The sequential centrifuging method developed in this contract to consolidate slurry powders is very convenient for testing new microstructures. However, in nonautomated systems it is very slow and labor-intensive, while in automated systems it would be limited mainly to axisymmetric shapes. An alternative slurry consolidation route, using the same colloidal systems but using sequential vacuum slip casting instead of centrifuging, yielded comparable results. This method can be faster for limited component thicknesses. It is also more versatile for producing more complex shapes and has potential to be adapted to rapid free-forming of complex components by laser scanning driven by a CAD file of the component. Another approach, based on tape casting instead of colloidal processing, is also under development in collaboration with two companies. In one of these collaborations, the company DSM is producing tapes of  $Ce-ZrO_2$  and  $Al_2O_2$ , while the consolidation and sintering conditions are being developed in collaboration with Prof. F. Lange and graduate student C. Hillman at the University of California at Santa Barbara. The other

collaboration involves Lone Peak Engineering (Utah), who are using tape-cast layers of Ce-ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> with a “laminated object manufacturing” method in which the individual tapes are cut as they are stacked using a laser that is controlled by a CAD file to produce complex shaped components directly.

## 2.0 Summary of Research

### 2.1 Crack Resistance Curves in Layered Ce-ZrO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> Ceramics

During the previous year, we demonstrated that very high fracture toughnesses (~18 MPa.m<sup>1/2</sup>) could be achieved in multilayered composites of Al<sub>2</sub>O<sub>3</sub> and Ce-ZrO<sub>2</sub>. These composites were designed on the basis of micromechanics modeling. The toughening is due to martensitic transformation of zirconia from the tetragonal to the monoclinic phase around cracks. The modeling predicted that with certain dual scale microstructures, the shape of the crack tip transformation zone could be modified to increase the toughening. Initial experiments indicated that, in addition to truncating the zone ahead of the crack tip as predicted, the presence of the Al<sub>2</sub>O<sub>3</sub> layers caused the transformation zone in the zirconia to spread along the region adjacent to the layers, thus increasing the zone width by up to a factor of 10 and further enhancing the toughness.

To explore the influence of layer dimensions and matrix properties on the toughening, a series of composites with various layer thicknesses and with Ce-ZrO<sub>2</sub> materials of two different initial fracture toughnesses were fabricated. These composites contained multilayered regions embedded in uniform Ce-ZrO<sub>2</sub> to allow controlled crack growth experiments within both layered and nonlayered materials in the same specimen. This allowed direct measurement of the toughening due to the layers, with the assurance that all other influences were equal. The R-curve measurements were obtained using notched beams loaded in flexure, with in situ measurement of crack growth and transformation zone development. The results indicated that the toughening, and in particular the slope of the R-curve, was insensitive to the layer thicknesses in the range 20 to 70 μm, and that the toughening increased as the transformability of the Ce-ZrO<sub>2</sub> matrix increased.

The peak toughness in these studies, while substantially increased over that of the base material (to 18 MPa.m<sup>1/2</sup> from ~5 MPa.m<sup>1/2</sup>), was limited by the finite number of layers in the test specimens (typically 20 layers), and the limited specimen thicknesses (~6 mm). Substantial effort was devoted to improving the colloidal method used to fabricate the multilayered structures. The method, developed in collaboration with F.F. Lange (UC Santa Barbara), involved sequential centrifugal consolidation of the Al<sub>2</sub>O<sub>3</sub> and Ce-ZrO<sub>2</sub> powders. The key requirements for achieving large fully dense, crack-free composites is to obtain very uniform

powder packing. Disk-shaped specimens with dimensions  $\sim 70 \times 15$  mm containing  $\sim 300$  layers were fabricated for further studies.

## **2.2 Mechanisms of Toughness Enhance in Zirconia-Based Laminar Composites**

Two effects contribute to the large toughness enhancement in multilayered  $\text{Al}_2\text{O}_3/\text{ZrO}_2$  composites. One is a truncation of the transformation zone ahead of the crack, as predicted by our previous analysis. The other, which was not predicated, is the spreading of the zone sideways along the layers. Several factors potentially contribute to the sideways spreading: (1) the modification of stresses adjacent to the crack by the presence of a nontransforming layer; (2) further modification of these stresses by the difference in elastic modulus of the  $\text{Al}_2\text{O}_3$  and  $\text{ZrO}_2$  layers; or (3) residual stresses due to thermal expansion mismatch. Although substantial residual stresses exist in these composites ( $\sim 100$  MPa in composites with  $\text{ZrO}_2$  and mixed  $\text{Al}_2\text{O}_3\text{-ZrO}_2$  layers), these are thought not to be the major cause of zone spreading: the spreading was observed also in specimens containing only isolated layers of  $\text{Al}_2\text{O}_3\text{-ZrO}_2$ , for which the residual stress in the  $\text{ZrO}_2$  matrix was negligible.

The influence of the first two mechanisms was assessed using a finite element analysis. The results indicated that the presence of a nontransforming layer near the crack tip causes very little change in hydrostatic stress components around the perimeter of the transformation zone, regardless of whether or not there is a difference in elastic modulus. However, the large shear stress concentration at the position where the spreading of the transformation zone was observed (Fig. 1) is consistent with the postulate that the transformation is initiated by shear. The stress concentrations were almost the same for the two cases evaluated, one with equal elastic moduli for both layers and the other with the stiffness of the nontransforming layer being double that of the transforming material, corresponding to the  $\text{Al}_2\text{O}_3/\text{ZrO}_2$  system. Therefore, the higher stiffness of the alumina layers is not an important factor.

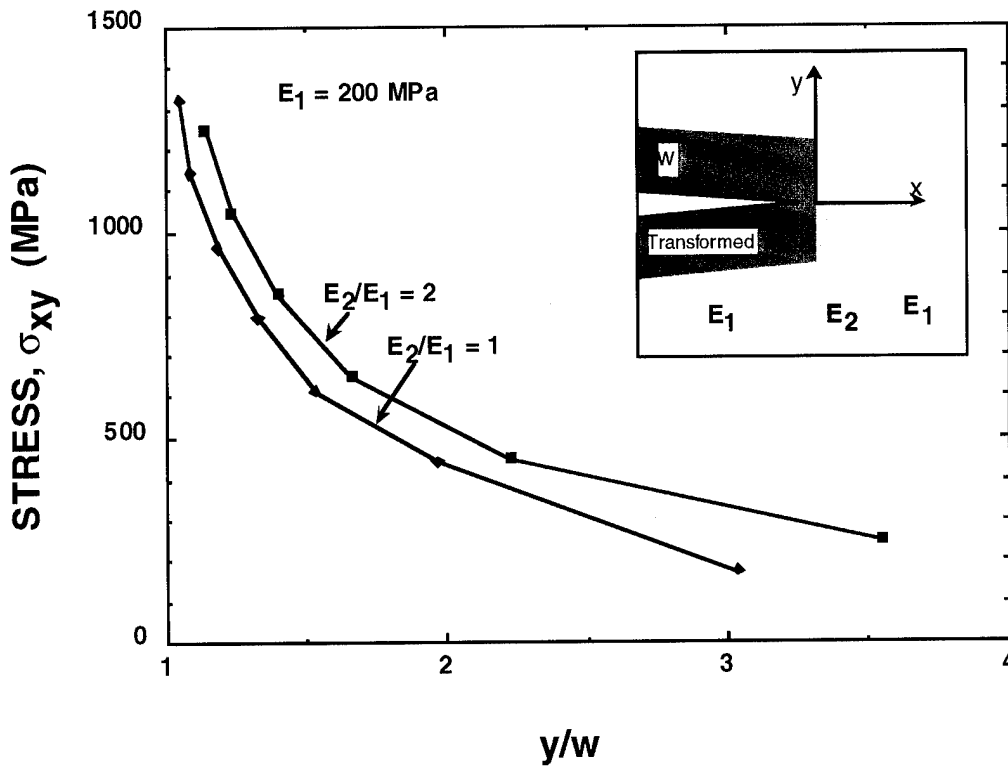


Fig. 1. Shear stress concentration adjacent to nontransforming layer ahead of crack tip in transformation toughened zirconia.

The stress concentration due to the nontransforming layer provides stresses above the known initiation stress for transformation (~400 MPa) over a distance about equal to the transformation zone width (Fig. 1). This indicates that the stress concentration exists over a sufficiently large volume of material to effect initiation of transformation. Once this occurs, continued growth of the transformation along the layer would be expected, because of autocatalytic effects and because the stress concentration would shift along ahead of the transformation.

### 2.3 Transformation Mechanisms and Optimum Layer Thicknesses in Multilayered Zirconia Composites

To investigate the effect of layer thickness on the extent of sideways spreading of the transformation zone in multilayered zirconia composites, specimens containing layers of  $ZrO_2$

and  $\text{Al}_2\text{O}_3/\text{ZrO}_2$  of various thicknesses were fabricated. This allowed investigation of relative transformation zone widths with all other experimental variables held constant.

Relative zone widths in layers of different thickness were measured under various conditions: (1) growth of cracks in notched beams, with in situ observation using high resolution Nomarski interference; (2) indentation with a Vickers indenter, and (3) controlled cooling with in situ observation by Nomarski interference. The results indicated that the extent of transformation is maximum for  $\text{ZrO}_2$  layer thicknesses in the range  $\sim 15$  to  $70 \mu\text{m}$  (Fig. 2), corresponding to  $\sim 5$  to 20 times the grain size of the transforming  $\text{ZrO}_2$ . At layer thicknesses above this range, transformation occurred in isolated bands traversing the layers as shown in Fig. 2, while at layer thicknesses below the range, the extent of transformation was less. The results were attributed to the effect of autocatalytic transformation: at layer widths below a few times the grain size the autocatalytic transformation is ineffective; while at layer thicknesses above  $\sim 20$  times grain size, there are an excess of nucleation sites that are able to initiate separate transformation bands ahead of an advancing transformation front, which in turn cause the front to arrest.

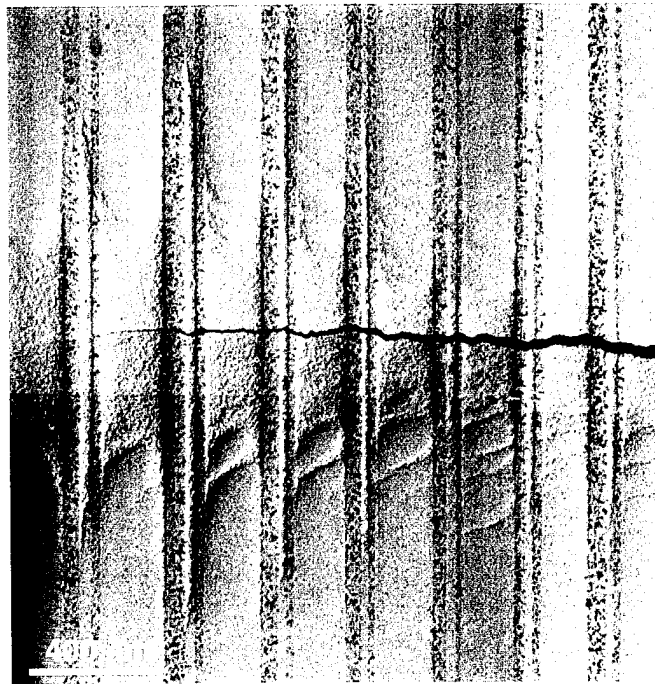


Fig. 2. Nomarski interference micrograph showing transformation zone in multilayered Ce- $\text{ZrO}_2/\text{Al}_2\text{O}_3$  composite: note more extensive transformation in narrower  $\text{ZrO}_2$  layers ( $\sim 30 \mu\text{m}$  thickness) and banded structure in wider layers.

**2.4 Crack Growth Mechanisms in Laminar Zirconia Composites**

In situ observations of crack growth during R-curve measurements in Al<sub>2</sub>O<sub>3</sub>/ZrO<sub>2</sub> multilayered composites indicated that in some composites, cracks grew by continuous advance of the crack tip; while in others cracks initiated in Al<sub>2</sub>O<sub>3</sub> layers ahead of the main crack and linked back to the main crack tip. The latter mechanism, which limits the toughness achievable, tended to occur in composites with some porosity in the Al<sub>2</sub>O<sub>3</sub> layers.

The transition in cracking mechanism was modeled as a competition of tunnel cracking in the intact Al<sub>2</sub>O<sub>3</sub> layer ahead of the main crack tip and direct advance of the shielded main crack tip. As the degree of toughening due to the transformation zone increases (due for example to changing test temperature or to heat treatment used to increase the transformability of the zirconia), the stress driving tunnel cracking in the Al<sub>2</sub>O<sub>3</sub> layer ahead of the main crack increases. A failure map defines the transition condition (i.e., the maximum toughness) in terms of two dimensionless parameters (Fig. 3):  $c_0/t$ , the ratio of size of defects in the Al<sub>2</sub>O<sub>3</sub> layers to the thickness of the ZrO<sub>2</sub> layers; and  $\alpha = \frac{\sigma_R + \sigma_T}{\sigma_0}$  where  $\sigma_R$  and  $\sigma_T$  are the stresses in the Al<sub>2</sub>O<sub>3</sub> layer due to thermal expansion mismatch and to a transformed layer of ZrO<sub>2</sub>, and  $\sigma_0$  is the tunneling stress in the alumina layer. The results indicate that this upper bound and the toughness are increased by reducing the sizes of defects in the Al<sub>2</sub>O<sub>3</sub> layers and/or reducing the Al<sub>2</sub>O<sub>3</sub> layer thickness.


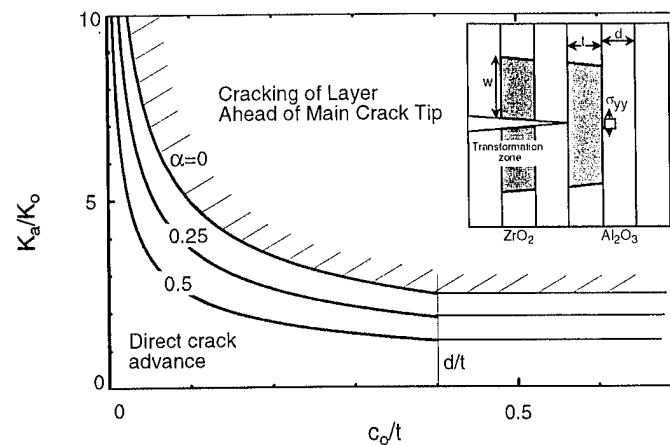


Fig. 3. Failure map showing transition in crack tip advance mechanism (which also defines the maximum toughness achievable).

## 2.5 Temperature Dependence of Toughening in Layered Zirconia Composites

The degree of transformation toughening in  $ZrO_2$  materials is well-known to decrease with increasing test temperature. To measure the sensitivity of the enhanced toughening in the laminar composites to test temperature, R-curves were measured at various temperatures between the  $M_s$  temperature (the temperature at which the martensitic tetragonal-to-monoclinic transformation occurs spontaneously) and room temperature, using several different materials that had different  $M_s$  temperatures within the range  $0^\circ\text{C}$  and  $-150^\circ\text{C}$ . These measurements were made using a loading fixture on the stage of an optical microscope, which allowed measurement of crack growth and transformation zone dimensions in situ. Cooling was achieved using circulating cold nitrogen.

The degree of toughening and the size of the crack tip transformation zone were very sensitive to the difference between the test temperature and the  $M_s$  temperature, as illustrated in Fig. 4. The very large transformation zones such as in Fig. 4 (b) and (c) and toughnesses above  $15 \text{ MPa}\cdot\text{m}^{1/2}$  were observed only for test temperatures within about  $100^\circ\text{C}$  of the  $M_s$  temperature. Therefore, applications that could take advantage of the extraordinarily high toughnesses achievable in these systems would be restricted.

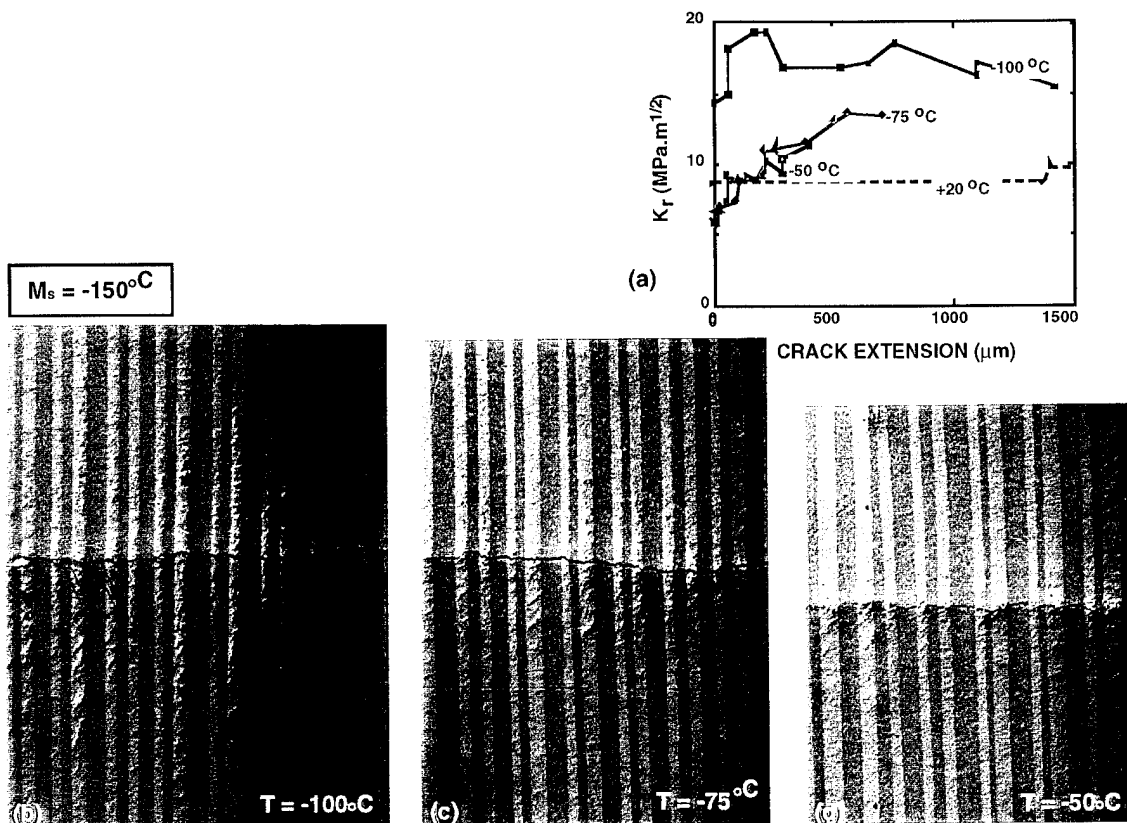

4. Temperature dependence of toughening in multilayered  $\text{Ce-ZrO}_2/\text{Al}_2\text{O}_3$  composite:  
 (a) Crack resistance curves measured at various temperatures.  
 (b) – (d) Nomarski interference micrographs showing transformation zones from specimens in (a).

## 2.6 Hardness-Size Effects and Residual Stresses in Multilayered $\text{ZrO}_2/\text{Al}_2\text{O}_3$ Composites

Contact damage pertinent to wear and abrasion in multilayered  $\text{Ce-ZrO}_2/\text{Al}_2\text{O}_3$  composites was assessed using Vickers indentation. For contact areas much larger than the layer thickness, the hardness was given by average of the hardnesses of the individual layers, weighted by the relative layer thicknesses. For contact areas comparable with the layer dimensions, the hardness did not scale with the relative fractions of the two layers within the contact area. Instead, it scaled with the relative volume fractions within the surrounding plastic zone. This resulted in a higher hardness than expected based on contact area for contact sites centered in the softer  $\text{ZrO}_2$  layers and lower hardness for those centered in the harder  $\text{Al}_2\text{O}_3$  layers.

Residual stresses due to thermal expansion mismatch in multilayered composites containing layers of Y-ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> were detected via their influence on Vickers indentation cracks. The results confirmed expected trends: parallel to the layers, the thermal mismatch generated tension in the ZrO<sub>2</sub> layers and compression in the Al<sub>2</sub>O<sub>3</sub> layers; whereas normal to the layers, surface effects generated tension in the Al<sub>2</sub>O<sub>3</sub> layers and compression in the ZrO<sub>2</sub> layers.

## **2.7 Indentation Studies of Y<sub>2</sub>O<sub>3</sub>-Stabilized ZrO<sub>2</sub>**

Cracks induced by indentation with a Vickers indenter are commonly used for measurement of fracture toughness in ceramics, including transformation toughened zirconia. However, the strains associated with the tetragonal-to-monoclinic transformation at the indentation side are not accounted for in previous analyses used to calculate the toughness. A study was undertaken to assess the amount of transformation induced by indentation and its influence on the evolution of the cracks, the crack shape and toughness measurements. The analysis of indentation cracking that is used to evaluate fracture toughness was revised to account for the presence of transformation strain. This work was done in collaboration with Prof. A.H. Heuer and Ms. M.S. Kaliszewski at Case Western Reserve University, as well as several others listed as co-authors on the paper of the same title listed in Section 1. Ms. Kaliszewski, a graduate student, visited Rockwell Science Center to perform some of her experimental work.

## **2.8 Damage Accumulation and Cyclic Fatigue in Mg-PSZ at Hertzian Contacts**

Irreversible damage caused by Hertzian contact (monotonic and cyclic) in three Mg-PSZ materials that had been heat-treated to different states was investigated. Analytical techniques, including optical and scanning electron microscopy, acoustic emission, Raman spectroscopy and thermal wave imaging, showed that the damage mechanisms were fundamentally different in three aging states. The dominant damage mechanisms were: microfracture in as-fired material (material in which tetragonal precipitates are not easily transformed to the monoclinic phase); tetragonal-to-monoclinic transformation in peak aged material (material of highest toughness, in which tetragonal precipitates are easily transformed); and monoclinic phase twinning in over-aged material (material in which most precipitates are already transformed from the tetragonal to the monoclinic phase). This work was done in collaboration with the group at NIST led by Dr. B.

Lawn; Dr. A. Pajares, a visiting scientist, spent time at Rockwell Science Center performing Raman spectroscopy and optical microscopy.

## 2.9 Debonding in Multilayered Composites of Zirconia and LaPO<sub>4</sub>

An alternative approach to transformation toughening for toughening brittle composites is to introduce interfaces or layers that debond when intercepted by a crack (interfaces in the Al<sub>2</sub>O<sub>3</sub>/ZrO<sub>2</sub> layered composites are strong and showed no evidence of debonding). This mechanism has the advantage that it is not temperature sensitive as is the transformation mechanism; but the disadvantage that weak interfaces lead to low transverse strength. Following our discovery in another program that LaPO<sub>4</sub> forms a weak interface with Al<sub>2</sub>O<sub>3</sub>, we explored the bonding and stability of LaPO<sub>4</sub> with several ZrO<sub>2</sub> systems, with the possibility in mind of combining toughening due to transformation and debonding. Multilayered composites were fabricated with alternating layers of LaPO<sub>4</sub> and ZrO<sub>2</sub> that was partially stabilized with either CeO<sub>2</sub> or Y<sub>2</sub>O<sub>3</sub>, or with 2-phase Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> layers. Debonding and distributed damage was observed in all cases (Fig. 5). The LaPO<sub>4</sub> and Y<sub>2</sub>O<sub>3</sub>-stabilized ZrO<sub>2</sub> layers were stable in air, with no interdiffusion detected at temperatures up to 1600°C. However, in the CeO<sub>2</sub>-stabilized system, interdiffusion of Ce and La occurred, leading to formation of (Ce, La) magnetoplumbites. The results suggest that CePO<sub>4</sub> may be a better interlayer for CeO<sub>2</sub>-stabilized zirconia.

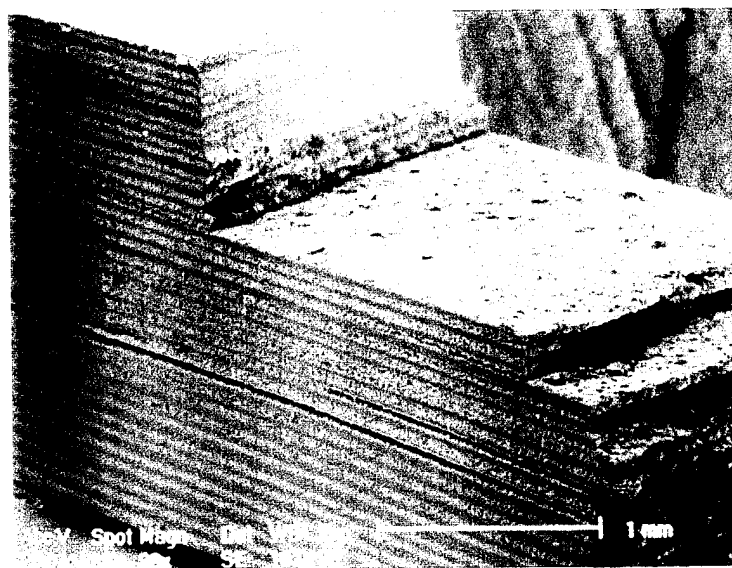


Fig. 5. Broken beam of multilayered Ce-ZrO<sub>2</sub>/LaPO<sub>4</sub>, showing delamination at LaPO<sub>4</sub> layers.

## **2.10 Fatigue Crack Growth and Stress Redistribution at Interfaces**

The role of the interface in redistributing stress around cracks in multilayered composites with alternating brittle and ductile components was investigated. The validity of models for the role of debonding and slip on stress redistribution was examined by comparing predictions with stresses measured by fluorescence spectroscopy. Debonding was substantially more effective than slip at reducing the stress. Under fatigue loading of these composites, two competing mechanisms were observed: mixed mode cracks extended along the metal/ceramic interfaces normal to the tip of the main crack (thus reducing the stresses ahead of the crack); while intact metal ligaments bridging the crack ruptured rapidly by Mode I fatigue crack growth (thus increasing the crack tip stress). This duality in fatigue behavior might be exploited to optimize the fatigue resistance of metal ceramic multilayers. This work was done as part of the Ph.D. thesis of Dr. M.C. Shaw, in collaboration with Prof. A.G. Evans at the University of California, Santa Barbara, while Dr. Shaw was employed at Rockwell. The experimental work was done at Rockwell Science Center.

### **3.0 Transition of Accomplishments to Industry**

We are collaborating with two companies to examine the feasibility of producing multilayered components based on the composites developed in this program. Tape-casting fabrication methods are being developed because of their potential versatility for producing shaped components. One company, DSM, is producing tapes of Ce-ZrO<sub>2</sub> and mixed Ce-ZrO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub>, while the consolidation and sintering conditions are being developed in collaboration with Prof. F. Lange and graduate student C. Hillman at the University of California at Santa Barbara. The other company, Lone Peak Engineering (Utah), are using tape-cast layers of Ce-ZrO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>/Ce-ZrO<sub>2</sub> with a "laminated object manufacturing" method, in which the individual tapes are cut as they are stacked using a laser that is controlled by a CAD file; this method produces complex shaped components directly from a series of slices from the computer file of the component. They have achieved dense multilayered microstructures with toughnesses of 10 MPa.m<sup>1/2</sup> and strengths of 700 MPa, a significant improvement over monolithic Ce-ZrO<sub>2</sub> or Al<sub>2</sub>O<sub>3</sub> fabricated by the same method (strength 540 MPa, toughness 6.7 MPa).

Rockwell's Rocketdyne Division are assessing the feasibility of a graded Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> composite rocket engine injector that would be fabricated using a free-form method; either the LOM method being developed by Lone Peak Engineering, or a colloiddally-based laser sintering method that we are exploring separately. Rockwell are also investigating 3-D photonic band gap structures that incorporate these materials with complex shapes produced by Lone Peak Engineering's laminated object manufacturing method.