

OFFICE OF NAVAL RESEARCH

GRANT: N00014-93-1-0615

R&T CODE: 3132081

Scientific Officer: Dr. Kenneth J. Wynne

TECHNICAL REPORT NO. 48

**Polarization Holographic Gratings in Azopolymers for Detecting and Producing
Circularly Polarized Light**

by

P. Rochon, V. Drnoyan and A. Natansohn

**Submitted for publication
in**

International Conference on Applications of Photonics Technology (SPIE)

**Department of Chemistry
Queen's University
Kingston, On., Canada**

June 23, 1998

**Reproduction in whole or in part is permitted for any purpose of the
United States Government**

**This document has been approved for public release and sale;
its distribution is unlimited.**

DTIC QUALITY INSPECTED 1

19980707 141

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Service, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE June 23, 1993	3. REPORT TYPE AND DATES COVERED Technical Report # 48		
4. TITLE AND SUBTITLE Polarization Holographic Gratings in Azopolymers for Detecting and Producing Circularly Polarized Light		5. FUNDING NUMBERS N00014-93-1-0615		
6. AUTHOR(S) P. Rochon, V. Drnoyan and A. Natansohn		8. PERFORMING ORGANIZATION REPORT NUMBER 48		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Department of Chemistry Queen's University Kingston, Ontario K7L 3N6 Canada		10. SPONSORING/MONITORING AGENCY REPORT NUMBER		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Department of the Navy Office of the Naval Research 800 North Quincy Street, Arlington, VA 22217-5000		11. SUPPLEMENTARY NOTES International Conference on Applications of Photonics Technology (SPIE)		
12a. DISTRIBUTION/AVAILABILITY STATEMENT Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.		12b. DISTRIBUTION CODE		
13. ABSTRACT (Maximum 200 words) Polarization holographic gratings were inscribed in azobenzene side chain polymer films. The polarization gratings were produced using two orthogonally circularly polarized beams and the resulting stable transmission gratings were studied using a low power HeNe laser. The gratings were observed to efficiently separate left and right circularly polarized light from the probe beam and two generate to elliptically polarized beams in the first order diffraction direction.				
14. SUBJECT TERMS Azobenzene polymers, holographic gratings, device, circularly, polarized light, separator		15. NUMBER OF PAGES 4		16. PRICE CODE
17. SECURITY CLASSIFICATION OF REPORT unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT unclassified	20. LIMITATION OF ABSTRACT unlimited	

Polarization holographic gratings in azopolymers for detecting and producing circularly polarized light.

P. Rochon

Department of Physics,
Royal Military College of Canada,
Kingston, Ontario K7K 7B4

V. Drmoyan and A. Natansohn

Department of Chemistry,
Queen's University
Kingston Ontario K7L 3N6

ABSTRACT

Polarization holographic gratings were inscribed in azobenzene side chain polymer films. The polarization gratings were produced using two orthogonally circularly polarized beams and the resulting stable transmission gratings were studied using a low power HeNe laser. The gratings were observed to efficiently separate left and right circularly polarized light from the probe beam and to generate two elliptically polarized beams in the first order diffraction direction.

2. INTRODUCTION

The availability of materials in which optical anisotropy can be photoinduced has led to a number of interesting studies on the recording of polarization holograms¹⁻³. These are made by the interference of two beams recorded in the material where the interference pattern is not a variation of intensity but rather a variation in the polarization state of the resultant wave in the material. The local polarization of the light is then recorded in an optically anisotropic material. In the present paper we consider the case when the holographic recording beams are of equal intensity and are orthogonally circularly polarized. One of the interesting properties of the holographic grating produced by these two beams is that it diffracts the left (LCP) and right-hand (RCP) circularly polarized light from a probe beam into two separate directions^{4,5}. This can then lead to a simple device that could measure the total polarization state of an input beam over a wide wavelength range. The theory also predicts that this grating could be used to produce circularly polarized light of selected handedness again over a wide wavelength range. In the present study we consider the production of these holographic gratings in azobenzene side chain polymers.

Azobenzene side chain polymers have been shown to have large, stable birefringence can be optically induced using moderate power argon lasers and short exposure times⁶. The recording medium is a thin film (ca. 400 nm thick) which is made by spin coating the polymer which is dissolved in tetrahydrofuran onto a glass substrate. The azobenzene molecules are intrinsically anisotropic but they are initially deposited in random directions making the film amorphous and isotropic. The molecules can be made to change shape and direction by the process of photoisomerization. Upon exposure to linearly polarized light the molecules tend to re-align in a direction that is perpendicular to the polarization direction. This results in a local optical anisotropy that can be detected using a probe which does not cause photoisomerization but which is still sensitive to the local birefringence. The optically induced birefringence in side chain azopolymers is stable over extended periods (years), therefore the holographic gratings can be components of a polarization measurement system as long as the films are protected against erasure.

3. EXPERIMENT

The holographic polarization grating was produced by the superposition of two orthogonal circularly polarized beams as illustrated below:


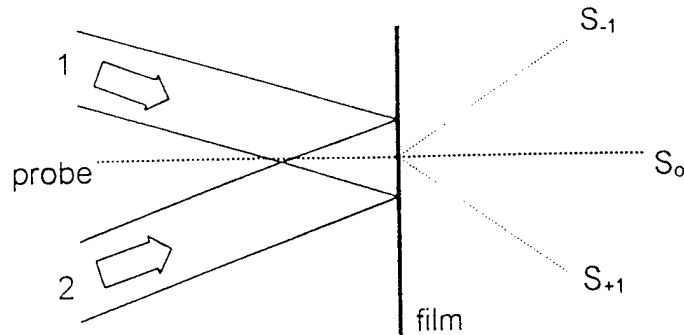


FIGURE 1: Optical set-up

The writing beams, 1 and 2, are from a 50 mW/cm^2 Argon laser at 488 nm and the probe beam is from a $10 \text{ }\mu\text{W}$ HeNe laser at 632.8 nm . The film was a side chain azopolymer⁵, pDR1M, which was cast onto a glass substrate. The writing beams are orthogonally circularly polarized to produce the following polarization patterns on the film:

2- LCP 1- RCP

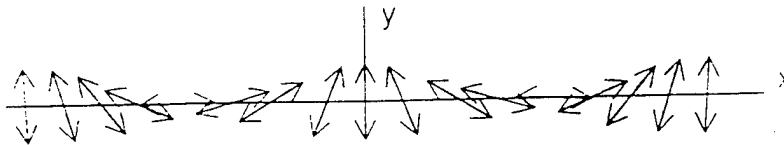

2- RCP 1-LCP

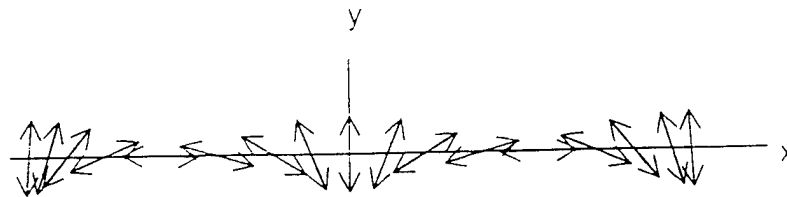


FIGURE 2 : Polarization gratings

We note that the first pattern is a rotation of the first pattern about the x-axis or z-axis (out of the paper). The angle between the writing beams was adjusted to give a grating spacing of about 6 micrometers. The polarization gratings were produced by writing for 100 seconds, which is enough time for the optically induced birefringence to reach saturation in these films. The birefringence was then allowed to relax in the dark for 500 seconds to reach the more stable long term birefringence levels of $\Delta n = 0.06$. The probe beam was then used to obtain the diffraction characteristics of the gratings. The probe beam polarization state was varied using a quarter wave plate and the polarization could be continuously varied from left circular to linear to right circular.

4. RESULTS AND DISCUSSION

The polarization grating can be described by the following transmission Jones matrix:

$$[T] = e^{i\phi_0} \left\{ \cos(\Delta\phi) \begin{pmatrix} 1 & 0 \\ 0 & 1 \end{pmatrix} + \sin(\Delta\phi) \frac{e^{i\delta}}{2} \begin{pmatrix} i & 1 \\ 1 & -i \end{pmatrix} + \sin(\Delta\phi) \frac{e^{-i\delta}}{2} \begin{pmatrix} i & -1 \\ -1 & -i \end{pmatrix} \right\}$$

Where ϕ_0 is the average phase delay through the film. $\Delta\phi = \pi d \cdot \Delta n / \lambda$ is the anisotropic phase delay due to the birefringence, and $\delta = 2\pi x / \Lambda$ is the phase delay along the grating with spacing Λ . In the above equation the first term in the brackets is the directly transmitted beam, the second term is the beam in the +1 order of diffraction and the third term is the beam in the -1 order of diffraction. One can readily see that in the above case a right circularly polarised beam of light, $\begin{bmatrix} 1 \\ -i \end{bmatrix}$ would only

be diffracted into the -1 order and that the resultant beam would be left circularly polarised. We have investigated this anisotropic diffraction property of the polarization gratings for circularly polarized light and the results are summarised in the following table which gives the direction and polarization state of the diffracted beams.

TABLE1: Diffraction of a circularly polarized probe beam

BEAM 1	RCP		LCP	
Probe	RCP	LCP	RCP	LCP
S ₊₁	-----	RCP	LCP	-----
S ₋₁	LCP	-----	-----	RCP

The results are in agreement with the above theoretical predictions. For example when Beam 1 of the writing beam is RCP and the probe beam is RCP then we observe that the diffracted beam occurs mostly in the -1 direction and the is it polarized LCP. The beam in the +1 direction is less than 2% of that in the -1 direction. When the probe beam is LCP then the light is diffracted into the +1 direction and is RCP. Also as indicated in the table, when the writing geometry or the sample geometry are inverted then the diffraction of the polarized beams is also affected.

The holographic grating is stable as long as the probe beam does not over write the inscribed information. The grating can then be used to measure the circular polarization content of a test light beam. In figure 3 we present the results of the diffraction efficiency into the +1 direction as a function of the PCP content of a test light beam. The intensity of the linearly polarized test beam was constant and rotating a quarter-wave plate varied the polarization state.

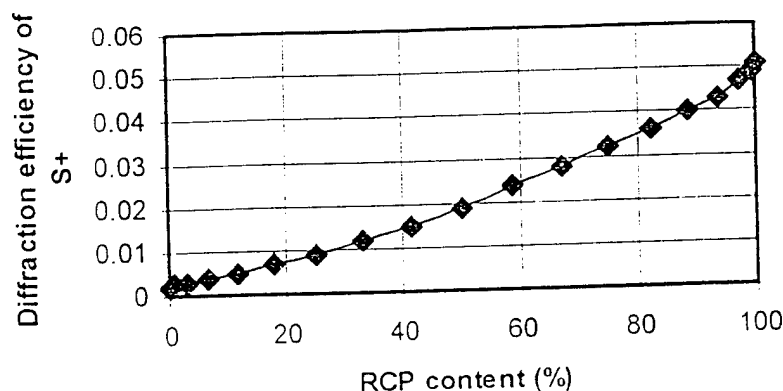


FIGURE 3: Polarization detection of a test beam

The results indicated that the polarization content of the test beam can be measured and that the polymer could be used in device applications. However, the diffraction efficiency was not linear with RCP content as was expected and it is possible that this indicates the although we attempted to prevent a surface relief grating from being formed during the holographic grating writing there may have been a weak grating formed never the less. This would also explain the non-zero value of the diffraction at zero content. This problem may be solve by using a different azo polymer which displays the same level of optically induced birefringence and yet is much less prone to the formation of surface relief gratings. The stability of the holographic grating can also be increased by using higher glass transition temperature polymers and chemical processing such as cross linking.

We have observed that the light diffracted in the -1 and -1 directions are not purely circularly polarized but are elliptically polarized and we believe that this is due to the chromophores which are aligned in the z -direction during the writing process. We are investigating this effect further since this may prove to be a valuable probe for the dynamics of those chromophores during the process of photoinduced birefringence.

5. ACKNOWLEDGEMENTS

Funding was provided by the Office of Naval Research USA, NSERC Canada, and the Department of National Defence of Canada.

6. REFERENCES

- 1- Sh.D. Kakichashvili Opt.Spectrosc. (1977) .42, p218-220
- 2- T. Todorov, L.Nikolova, and N. Tomova Appl. Optics (1984), 23, 4309-4312
- 3- J.J. Couture and R.A. Lessard, Appl. Optics (1988), 27, 3368-3374
- 4- L. Nikolova, T. Petrova, M. Ivanov, T. Todorov and E. Nacheva, J. Modern Optics, (1992), 39, 1953-1963
- 5- T. Todorov and L. Nikolova, Opt. Letts. (1992), 17, 358-359
- 6- A. Natansohn and P. Rochon, ACS symposium series 672 , Photonic and Optoelectronic Polymers, (1997), 236-250
- 7- F. Lagugne-Labert, T. Buffeteau and C. Sourisseau, J. Phys. Chem , (1998), B102, 2654-2662.