

AD

TECHNICAL REPORT ARCCB-TR-99018

**LOADING FREQUENCY AND ITS EFFECTS
ON THE FATIGUE LIFE OF A723 STEEL**

**E. TROIANO
C. MOSSEY
J. H. UNDERWOOD**

OCTOBER 1999



**US ARMY ARMAMENT RESEARCH,
DEVELOPMENT AND ENGINEERING CENTER
CLOSE COMBAT ARMAMENTS CENTER
BENÉT LABORATORIES
WATERVLIET, N.Y. 12189-4050**



APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

19991102 000

DTIC QUALITY INSPECTED 4

DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

The use of trade name(s) and/or manufacturer(s) does not constitute an official endorsement or approval.

DESTRUCTION NOTICE

For classified documents, follow the procedures in DoD 5200.22-M, Industrial Security Manual, Section II-19, or DoD 5200.1-R, Information Security Program Regulation, Chapter IX.

For unclassified, limited documents, destroy by any method that will prevent disclosure of contents or reconstruction of the document.

For unclassified, unlimited documents, destroy when the report is no longer needed. Do not return it to the originator.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE October 1999	3. REPORT TYPE AND DATES COVERED Final		
4. TITLE AND SUBTITLE LOADING FREQUENCY AND ITS EFFECTS ON THE FATIGUE LIFE OF A723 STEEL			5. FUNDING NUMBERS AMCMS No. 4221.23.0000.0	
6. AUTHOR(S) E. Troiano, C. Mossey, and J.H. Underwood				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Benet Laboratories, AMSTA-AR-CCB-O Watervliet, NY 12189-4050			8. PERFORMING ORGANIZATION REPORT NUMBER ARCCB-TR-99018	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Close Combat Armaments Center Picatinny Arsenal, NJ 07806-5000			10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The fatigue life of pressure vessels manufactured from two strength levels (166 Ksi and 190 Ksi) of A723 steel has been modeled, and the life predictions using the model have verified that a field loading cycle is equivalent to a laboratory pressurization loading cycle. One key assumption in the model is that a minimum crack initiator must be present in order to attain a one-to-one correlation. If the minimum crack initiator is not present, there will be a large error between laboratory and field loading when predicting final fatigue failure. This study shows that a crack initiator greater than about 0.019 inch (for 166 Ksi yield strength steel) and 0.008 inch (for 190 Ksi yield strength steel) will result in the one-to-one correlation that is sought. No attempt has been made to model environmental effects that can greatly affect the results presented here.				
14. SUBJECT TERMS Frequency, Fatigue Life, Life Prediction, Crack Initiation			15. NUMBER OF PAGES 7	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UJL	

TABLE OF CONTENTS

	<u>Page</u>
INTRODUCTION.....	1
TEST RESULTS	2
ANALYSIS OF RESULTS.....	3
CONCLUSIONS	5
REFERENCES.....	6

TABLES

1. Results of da/dN Test Data for A723 Steel at Two Different Strength Levels.....	2
--	---

LIST OF ILLUSTRATIONS

1. Effects of frequency on fatigue	1
2. Frequency effects of A723 steel at yield strength 166 Ksi	4
3. Frequency effects of A723 steel at yield strength 190 Ksi	4

INTRODUCTION

Classic work in the field of fatigue states that there is a frequency effect on the cycles-to-failure that can be expected when metals are tested in laboratory air. This effect can be exacerbated by factors such as waveform of the load application and environmental effects, including moisture, hydrogen, etc. (ref 1). In general terms, if the frequency of loading is slower, then lesser lives can be expected. This is due to the fact that there is more exposure time to the environment (ref 2). Figure 1 isolates the frequency effects and identifies the results that can be expected in air and in a vacuum. Note that above a certain threshold (identified by the dotted line) there is no further increase in life as a result of increased frequency.

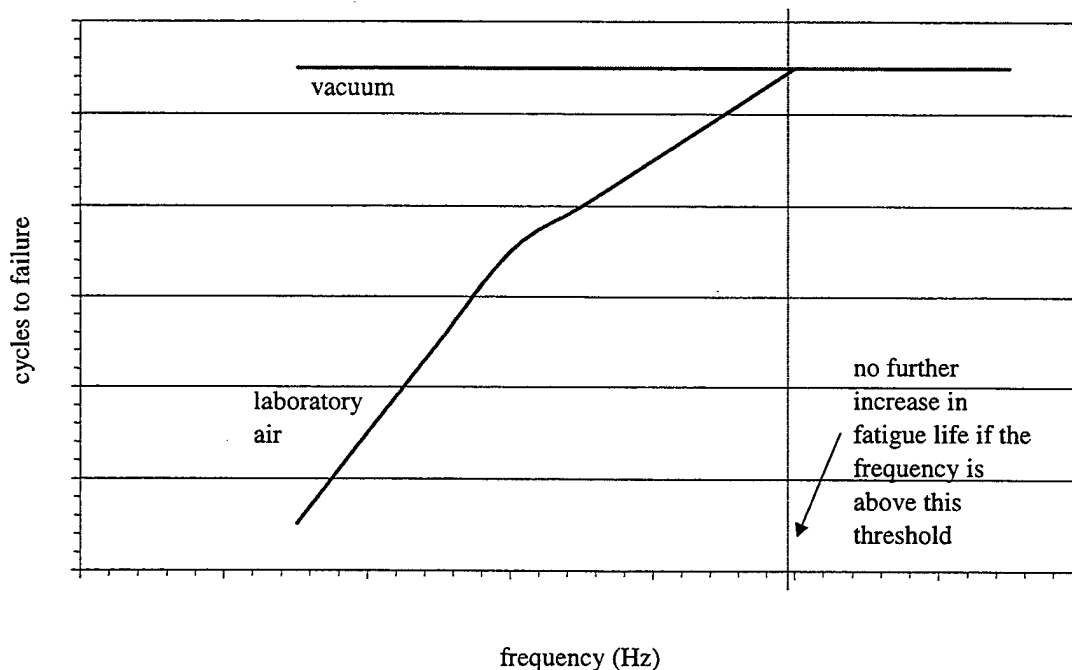


Figure 1. Effects of frequency on fatigue.

This study attempts to identify whether the cyclic frequency of loading between field loading and laboratory loading has any effect on the overall life of a gun tube. We have identified that the typical loading scenario of a field-loaded weapon is on the order of 200 Hz, while the typical fatigue loading in the laboratory for gun tubes is on the order of 0.3 Hz. Because of limitations with modern servohydraulic test machines, a loading rate of 200 Hz is impossible. Therefore, the loading rates that we could successfully test to were 0.3 Hz and 30 Hz. Remember, as stated in the previous paragraph, above a certain threshold there is no further increase in fatigue life as a result of increasing frequency. Therefore, if we successfully prove that there is no difference between 0.3 Hz and 30 Hz, then it is safe to assume that there is no difference between 0.3 Hz and 200 Hz.

TEST RESULTS

Testing was conducted with an Instron 10-kip servohydraulic test machine. A fully automated control program written by Fracture Technology Associates of Pennsylvania was utilized. The program was written to conform to ASTM Specification E647 for da/dN testing of metallic materials. A compact specimen (CT) geometry with the following dimensions was utilized for all tests: $W = 1.575$ inches; $t = 0.395$ inch; $H = 0.945$ inch; and notch depth = 0.350 inch. Premium A723 Grade 2 was the gun steel chosen. Because of an ever-increasing interest in higher strength A723 steel for future applications, two heat treatments were investigated, including the standard yield strength of 166 Ksi and a yield strength of 190 Ksi. All testing was conducted in load control, in laboratory air, at a temperature of $72^{\circ}\text{F} \pm 5^{\circ}\text{F}$, and at an R-ratio of 0.1.

The test results are shown in Table 1. These test results are not conclusive, in that they cannot be utilized in this form to approximate remaining life of a component. Further analysis presented in the next section will answer these questions.

Table 1. Results of da/dN Test Data for A723 Steel at Two Different Strength Levels

Specimen ID	0.2% Yield Strength (Ksi)	Frequency (Hz)	R-ratio	C	N
1	166	30	0.1	1.53E-10	2.94
2				3.29E-09	2.29
3				2.21E-10	2.87
4				1.41E-10	2.96
5				7.02E-10	2.63
11				1.77E-09	2.54
12				3.68E-10	2.87
Average				9.49E-10	2.73
6	166	0.3	0.1	1.97E-09	2.43
7				7.17E-09	2.11
8				6.23E-08	1.63
9				2.53E-09	2.25
10				4.90E-09	2.09
Average				1.58E-08	2.08
6	190	30	0.1	3.37E-09	2.26
7				1.43E-09	2.53
8				4.53E-10	2.86
9				1.42E-09	2.47
10				3.46E-09	2.37
11				4.16E-09	2.16
Average				2.38E-09	2.44
1	190	0.3	0.1	3.25E-09	2.29
2				1.61E-08	1.89
3				8.75E-09	2.02
4				8.16E-09	2.05
5				2.20E-08	1.79
Average	1.17E-08	2.01			

ANALYSIS OF RESULTS

The test results generated from ASTM Specification E647 can now be utilized with the well-known Paris Law

$$da / dN = C\Delta K^n \quad (1)$$

to approximate remaining life. This equation can be integrated with the approximate closed-form ΔK solution for a gun tube

$$\Delta K = \Delta\sigma\sqrt{\pi a} \quad (2)$$

to yield

$$N_f = \frac{1}{\left(\frac{-n}{2} + 1\right)(C\pi^{n/2}\Delta\sigma^n)} [a_f^{-n/2+1} - a_i^{-n/2+1}] \quad (3)$$

where a_i is the initial detectable flaw depth, a_f is the final or critical crack depth, $\Delta\sigma$ is the applied stress (approximated here as the yield strength), and N_f is the number of remaining cycles-to-failure.

K_{Ic} for the two heat treatments was known from prior experience to be 120 Ksi $\sqrt{\text{in}}$. for the 166 Ksi yield strength, and 90 Ksi $\sqrt{\text{in}}$. for the 190 Ksi yield strength. These values coupled with the ΔK solution, yield an a_f of 0.166 inch for the 166 Ksi yield strength and 0.071 inch for the 190 Ksi yield strength.

Utilizing these inputs, we can formulate an expression for remaining life of the gun tube versus the initial detectable flaw size, a_i . The results of this formulation can be observed in Figure 2 (166 Ksi yield strength) and Figure 3 (190 Ksi yield strength). Note how sensitive the calculations for remaining life are in response to the small initial flaw sizes. As a_i becomes increasingly smaller, the approximation between remaining life for the faster and slower loading rates becomes more prominent. For the 166 Ksi yield strength material, we can clearly see that an $a_i > 0.019$ inch results in remaining lives within 100 cycles for both loading rates, and for the 190 Ksi yield strength material, if $a_i > 0.008$ inch, the remaining life is also within 100 cycles for all initial flaw sizes. It is quite possible that these estimates of a_i are overly conservative because the ΔK expression utilized is not exact for a gun tube. Had an exact ΔK expression for gun tubes been available (for short and long cracks), it would have been utilized. The ΔK expression utilized does closely approximate a gun tube for moderate and long cracks, however it has limitations for small cracks, and severe limitations for extremely small cracks.

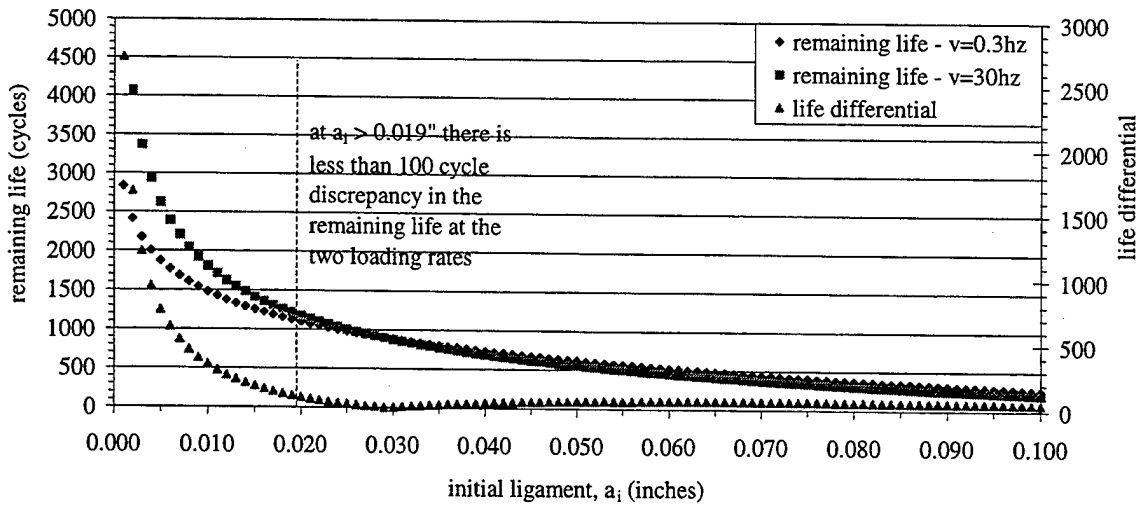


Figure 2. Frequency effects of A723 steel at yield strength 166 Ksi.

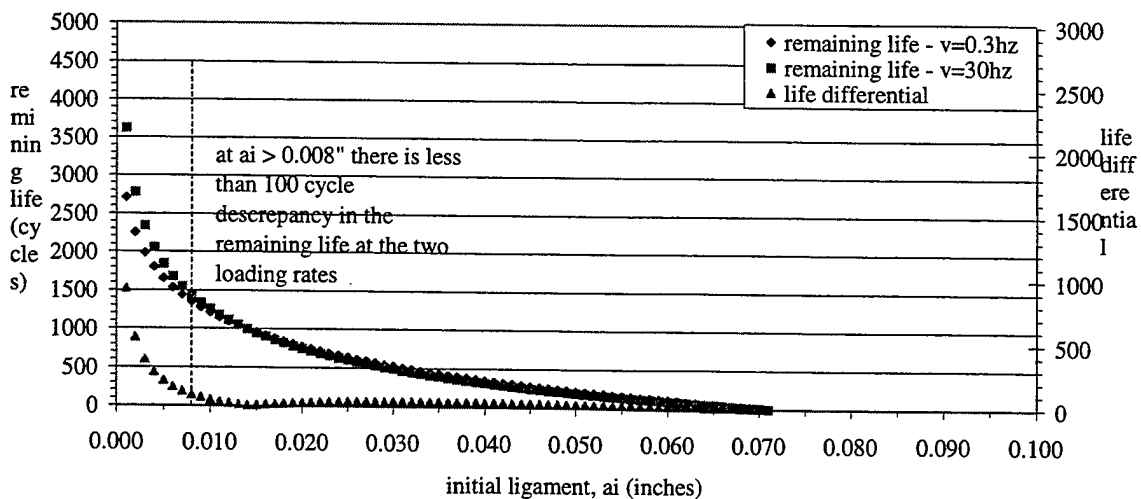


Figure 3. Frequency effects of A723 steel at yield strength 190 Ksi.

Since gun tubes are fired out in the field to induce the initial cracking, it is imperative that the initial depth of cracking be known prior to fatigue loading in the laboratory. For example, if the initial flaw depth from firing in the field were 0.002 inch and the tube was fired in the field until failure (200 Hz), the approximate life would be 4070 cycles; whereas if that same tube had been returned to the lab for fatigue cycling (0.3 Hz), the expected life would have been 2410 cycles. However, if the initial flaw depth from field firing were 0.020 inch, the expected life would be 1180 cycles in the field (200 Hz) and 1100 cycles in the lab (0.3 Hz).

CONCLUSIONS

1. This study assumes only mechanical frequency effects, and does not address environmental factors, which can greatly impact the life of a gun tube.
2. Initial flaw depth from field firing must be known in order to approximate remaining life. This requirement becomes more important as the initial crack depth goes to 0.000 inch.
3. As the initial flaw depth increases, the approximation of remaining life as a result of frequency effects becomes less prominent. For gun steel with a yield strength of 166 Ksi and an initial flaw depth greater than 0.019 inch, there is a one-to-one correlation between field loading (200 Hz) and laboratory loading (0.3 Hz). For 190 Ksi yield strength gun steel, there is a one-to-one correlation for any flaw depth greater than 0.008 inch.
4. For all practical purposes, the approximation of estimating initial flaw depths with ultrasonics is on the order of 0.015 to 0.020 inch. Hence, the flaw depths recommended above are not easily detectable in the field.
5. We know that the initial field firing of a cannon is necessary to induce cracking, and this analysis has shown that the initial flaw size for our current strength gun steels is on the order of 0.019 inch for a one-to-one correlation between field and laboratory loading. This value is likely conservative since the ΔK expression utilized in equation (2) is approximate for a gun tube, and is not ideally suited for extremely short cracks. As the initial crack depth goes toward zero, the error imposed by this approximation becomes more prominent. Since the results showed little frequency effects for longer cracks, where these expressions, and the data are known to be accurate and correct, we believe that the conservatism's built into the analysis may not be justified. Therefore, we feel that any detectable cracking of a gun tube is sufficient for a one-to-one correlation between laboratory and field loading.

REFERENCES

1. Coffin, L., Dr., Notes, Rensselaer Polytechnic Institute, Troy, NY, 1990.
2. Dowling, N.E., *Mechanical Behavior of Materials*, Prentice Hall, 1993.

TECHNICAL REPORT INTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>
TECHNICAL LIBRARY ATTN: AMSTA-AR-CCB-O	5
TECHNICAL PUBLICATIONS & EDITING SECTION ATTN: AMSTA-AR-CCB-O	3
OPERATIONS DIRECTORATE ATTN: SIOWV-ODP-P	1
DIRECTOR, PROCUREMENT & CONTRACTING DIRECTORATE ATTN: SIOWV-PP	1
DIRECTOR, PRODUCT ASSURANCE & TEST DIRECTORATE ATTN: SIOWV-QA	1

NOTE: PLEASE NOTIFY DIRECTOR, BENÉT LABORATORIES, ATTN: AMSTA-AR-CCB-O OF ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
DEFENSE TECHNICAL INFO CENTER ATTN: DTIC-OCA (ACQUISITIONS) 8725 JOHN J. KINGMAN ROAD STE 0944 FT. BELVOIR, VA 22060-6218	2	COMMANDER ROCK ISLAND ARSENAL ATTN: SIORI-SEM-L ROCK ISLAND, IL 61299-5001	1
COMMANDER U.S. ARMY ARDEC ATTN: AMSTA-AR-WEE, BLDG. 3022 AMSTA-AR-AET-O, BLDG. 183 AMSTA-AR-FSA, BLDG. 61 AMSTA-AR-FSX AMSTA-AR-FSA-M, BLDG. 61 SO AMSTA-AR-WEL-TL, BLDG. 59 PICATINNY ARSENAL, NJ 07806-5000	1 1 1 1 1 2	COMMANDER U.S. ARMY TANK-AUTMV R&D COMMAND ATTN: AMSTA-DDL (TECH LIBRARY) WARREN, MI 48397-5000 COMMANDER U.S. MILITARY ACADEMY ATTN: DEPT OF CIVIL & MECH ENGR WEST POINT, NY 10966-1792	1
DIRECTOR U.S. ARMY RESEARCH LABORATORY ATTN: AMSRL-DD-T, BLDG. 305 ABERDEEN PROVING GROUND, MD 21005-5066	1	U.S. ARMY AVIATION AND MISSILE COM REDSTONE SCIENTIFIC INFO CENTER ATTN: AMSAM-RD-OB-R (DOCUMENTS) REDSTONE ARSENAL, AL 35898-5000	2
DIRECTOR U.S. ARMY RESEARCH LABORATORY ATTN: AMSRL-WM-MB (DR. B. BURNS) ABERDEEN PROVING GROUND, MD 21005-5066	1	COMMANDER U.S. ARMY FOREIGN SCI & TECH CENTER ATTN: DRXST-SD 220 7TH STREET, N.E. CHARLOTTESVILLE, VA 22901	1
COMMANDER U.S. ARMY RESEARCH OFFICE ATTN: TECHNICAL LIBRARIAN P.O. BOX 12211 4300 S. MIAMI BOULEVARD RESEARCH TRIANGLE PARK, NC 27709-2211	1		

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER,
BENÉT LABORATORIES, CCAC, U.S. ARMY TANK-AUTOMOTIVE AND ARMAMENTS COMMAND,
AMSTA-AR-CCB-O, WATERVLIET, NY 12189-4050 OF ADDRESS CHANGES.
