

High-Performance Ultrafast Photodetectors

M. Selim Ünlü

Boston University, Photonics Center, 8 Saint Mary's St., Boston, MA 02215

Phone: (617) 353-1712, e-mail: selim@bu.edu, fax: (617) 353-9917

Grant No: ONR N00014-96-1-0652

Program Manager: Yoon Soo Park

FINAL REPORT

20000228 046

High-Speed High-Efficiency RCE Photodetectors

M. Selim Ünlü

Boston University, Photonics Center, 8 Saint Mary's St., Boston, MA 02215

Phone: (617) 353-1712, e-mail: selim@bu.edu

Grant No: ONR N00014-96-1-0652

Program Manager: Yoon Soo Park

1. Technical Objectives and General Approach

This project concentrates on the design, fabrication and characterization of compound semiconductor photodetectors in various material systems operating at near-IR wavelengths. We utilize resonant cavity enhanced (RCE)¹ detection scheme to optimize speed and responsivity of photodetectors. It is also desirable to combine multiple functions in a single photodetector structure. In addition to wavelength selectivity of RCE photodetectors, we have demonstrated that RCE detectors vertically integrated with one-pass detectors can be used for polarization sensing.

We have demonstrated RCE photodetectors working at 800-900 nm wavelength range with record bandwidth-efficiency products. In the following report we reference to the archival journal articles published under this funded program. The conference papers are listed at the end of the references.

2. RCE Schottky Photodiodes

Schottky photodiodes (PD) are very attractive for high-speed photodetection, since they have a simple material structure and fabrication thus allowing for easy integration with III-V discrete devices and integrated circuits. With the increasing demand for faster detector speeds, the optimized structure of a Schottky PD typically has a very thin absorption region. For front illuminated devices, a very thin Schottky metal is used so that light can penetrate the semi-transparent contact and reach the semiconductor. The resonant cavity enhanced (RCE) detection scheme is particularly attractive for Schottky type photodetectors since a semi-transparent contact can function also as the top reflector. RCE detectors with single-layer top mirrors are very desirable for post-growth adjustment of the resonant wavelength by simply recessing the top layer. We present theoretical and experimental results on spectral and high-speed properties of RCE Schottky photodiodes with semi-transparent top metal contacts.

We studied RCE Schottky diodes in GaAs/InGaAs material system operating at 900 nm wavelength (see Fig.1 for a schematic device structure)^{2,3}. Similar principles apply to other III-V materials and different wavelength regions. The devices were grown on GaAs substrates by molecular beam epitaxy (MBE). The absorption layer is InGaAs with an In mole fraction less than 10 % and a thickness of 130 nm to eliminate the standing wave effect in the cavity. The position of the absorption layer in the depletion region is optimized to yield minimum transit time for electrons and holes. The resonant cavity is formed by a GaAs/AlAs DBR bottom reflector and the semi-transparent Au contact on top. After the Schottky metal, a top dielectric layer (Si₃N₄) is deposited. This matching layer is critical in the optimization of the optical

responsivity. We consider only a single layer dielectric coating to maintain simple device fabrication.

We analyzed the dependence of responsivity on the thickness of the metal contact and the dielectric coating. By computer simulations, we demonstrated that these thicknesses can be optimized to yield nearly 75% quantum efficiency at resonance for this thin absorption region. Without a dielectric coating, the optimum Au thickness is about $150\text{\AA}$. For different dielectric top coatings (Si_3N_4) serving as impedance matching layers, the optimized Au layer thickness can cover a range from $150\text{\AA}$ to over $300\text{\AA}$. The capability to use thicker Schottky metal reduces the spreading resistance..

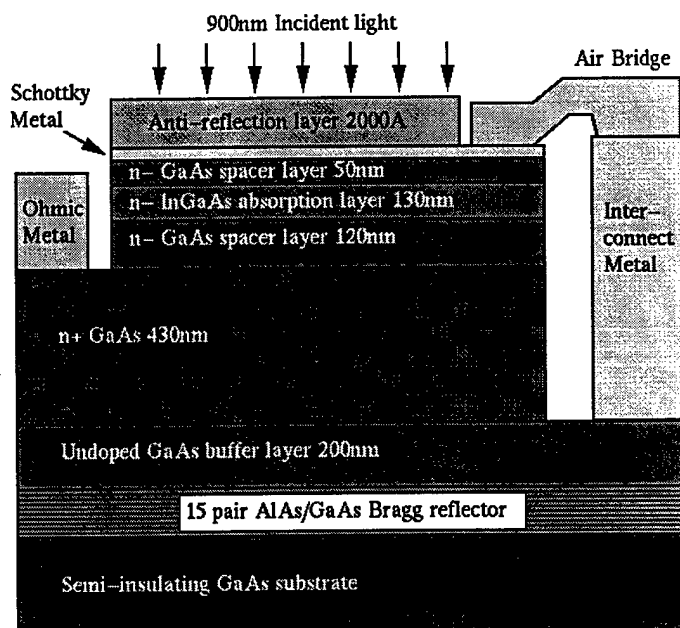


Fig. 1. Schematic layer structure of GaAs/InGaAs/AlAs RCE Schottky photodiode designed for 900 nm wavelength.

Photodiodes of various sizes were fabricated by standard photolithography with mesa isolation and a Au airbridge connecting the top contact to a co-planar transmission line. (See Figs. 2 and 3). The resulting devices showed breakdown voltages larger than 12 V. To emphasize the advantage of RCE detection, in Fig. 1, we also plot the quantum efficiencies of an optimized RCE Schottky PD and a conventional (one-pass) detector with identical absorption layer and metal

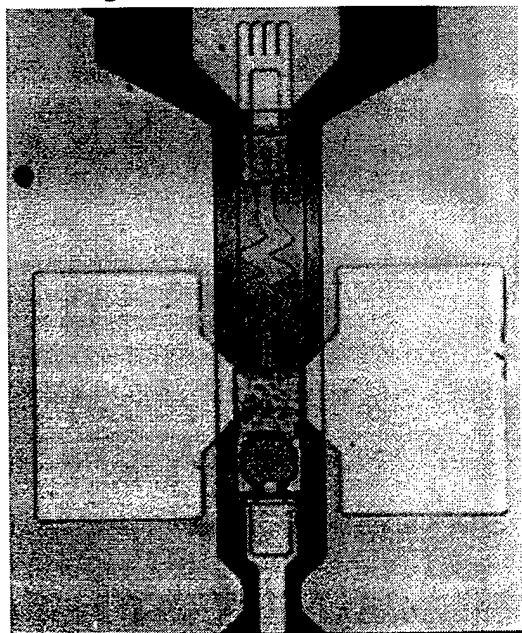


Fig. 2. Optical micrograph of typical RCE Schottky photodiodes fabricated using microwave co-planar transmission lines.

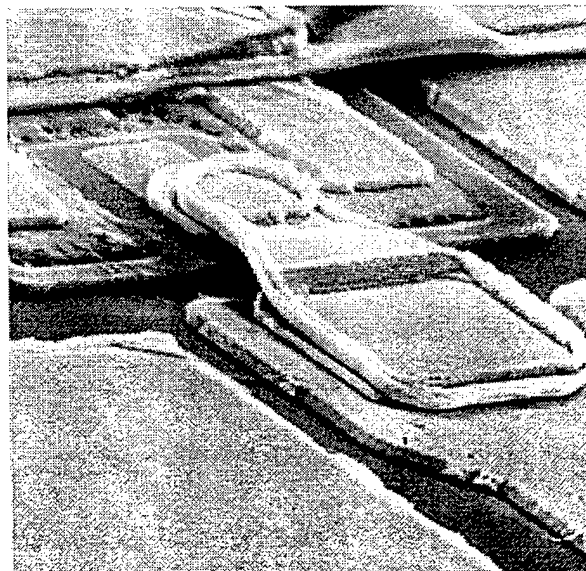


Fig. 3. Scanning Electron Microscopy picture of a RCE Schottky photodiode illustrating the air-bridge for top contact.

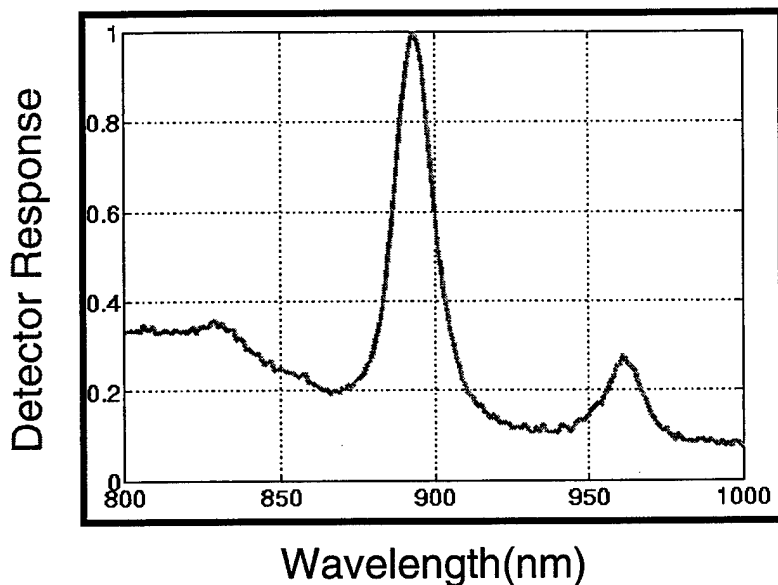


Fig. 4. Measured spectral response of RCE Schottky photodiodes. The detector response is normalized to unity. The peak efficiency is about 20%.

locked Ti:Sapphire laser. The devices were illuminated using a single mode fiber on a microwave probe station and the response at zero bias was observed with a 50 GHz sampling oscilloscope. For the wavelength dependence of the high-speed response, a $10 \times 10 \mu\text{m}$ device was studied. Figure 5 shows the pulse response obtained at 895 nm, where the incident light is absorbed only in the thin InGaAs absorber with the exception of the Schottky metal, the rest of the cavity is nearly lossless, and the device functions as a RCE Schottky PD. The FWHM of the pulse response as measured on the scope is 10 ps. The measured rise time, which is a characteristic of the measurement setup was 9 ps. The pulse responses observed on the scope correspond to the total system bandwidth and are limited by the speed of the sampling scope. Considering a 9 ps FWHM pulse width for the scope, and a 1.2 ps laser pulse width, the estimated detector impulse width is 4.1 ps. This is a conservative estimate since the microwave components in the signal path and laser timing jitter also contribute to the measured pulse width. The corresponding 3-dB bandwidth is in excess of 100 GHz. Together with the 3 fold increase in efficiency the bandwidth-efficiency product of the devices is improved by a factor of 6 at resonance. We have also designed and fabricated top illuminated AlGaAs/GaAs RCE Schottky PDs demonstrating a peak

thickness. Figure 4 shows the measured photoresponse spectra of the devices. The peak quantum efficiency was measured to be 18% at 895 nm whereas the expected value was above 70%. Nevertheless, when compared with a single-pass device the enhancement factor is 6, and the FWHM is 15nm. On similar devices operating around 850 nm wavelength⁴, where a more controlled experiment in terms of the Schottky metal thickness, and the absorption coefficient of the thin absorber was performed, efficiency values as high as 50% and a 25 GHz BWE were demonstrated.

High-speed measurements were performed using a picosecond mode-

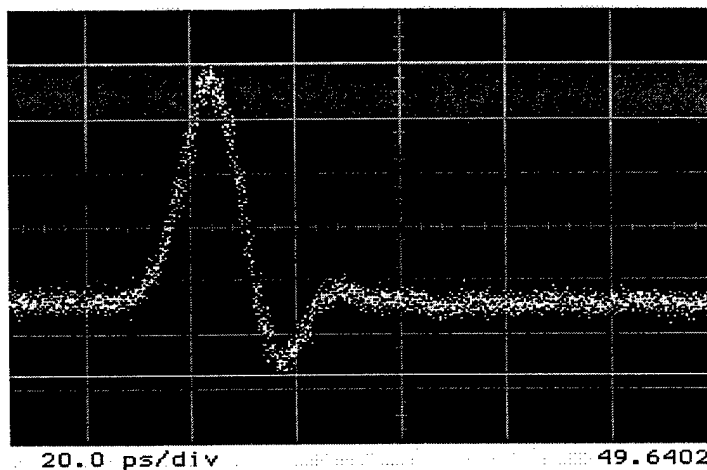


Fig. 5. Measured pulse response of RCE Schottky photodiodes.

quantum efficiency of $\eta=50\%$ and a 3-dB bandwidth of more than 50 GHz. The resulting BWE product is more than 25 GHz for operation wavelength in 800-850 nm wavelength region.⁴ We have recently published a review of our results on design and optimization of high-speed RCE Schottky photodiodes.⁵

3. RCE pin Photodiodes

We also studied GaAs/AlGaAs based high-speed, high-efficiency, resonant cavity enhanced (RCE) p-i-n photodiodes.^{6,7} Figure 5 shows a schematic representation of studied devices. Since the top surface is not metalized, one of the advantages of the p-i-n RCE photodetectors is that the quantum efficiency can be very high approaching unity. Also, by using a post-process recess-etch, we tuned the resonance wavelength from 835 nm to 795 nm while keeping the peak efficiencies above 90%.⁶ Figure 6 shows the adjustment of the resonance wavelength by recessing the top surface.

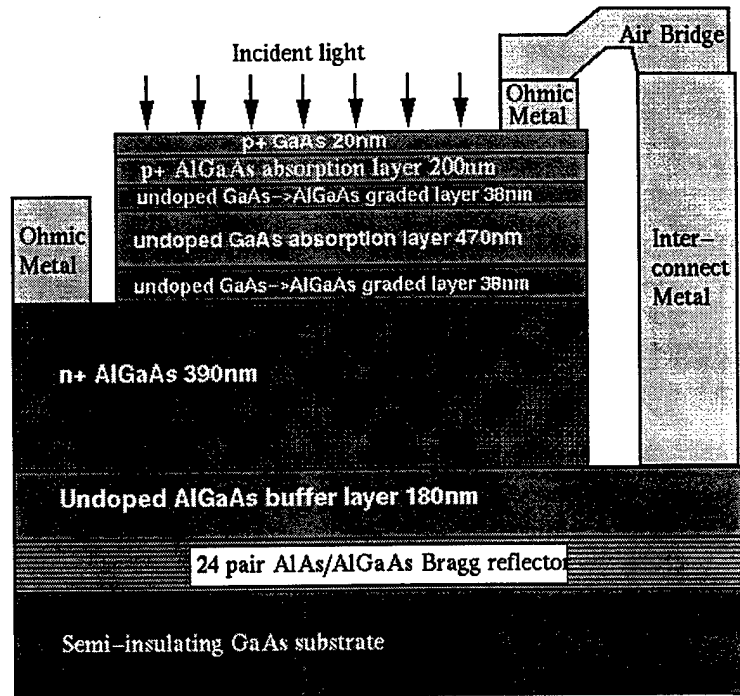


Fig. 5. Schematic layer structure of AlGaAs/GaAs/AlAs RCE p-i-n photodiode designed for 800-850 nm wavelength range

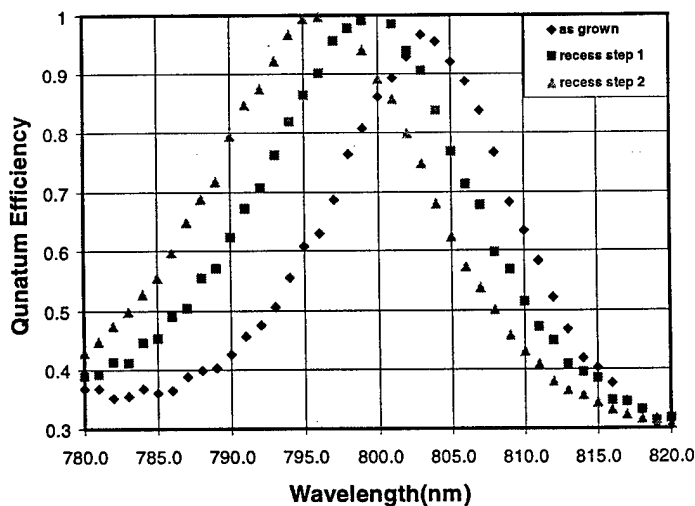


Fig. 6. Measured quantum efficiency of a near-unity efficiency GaAs/AlGaAs p-i-n PD for different recess etch steps.

The maximum measured quantum efficiency, was 100% with an experimental error margin of 2%.⁷ The fabricated photodiode had an experimental setup limited temporal response of 12 ps. When the system response is deconvolved, the 3-dB bandwidth corresponds to 50 GHz, which is in good agreement with our theoretical calculations. Our work on high-speed photodiodes has been included in Optics in 1999 issue of Optics & Photonics News.⁸

4. RCE photodetectors with a flat resonant peak

The spectral response limits the suitability of the high performance RCE detectors in optical communications where the emitter wavelength tolerances are not very stringent and in short-pulse applications where the source has a broad spectral content. We theoretically studied structures for attaining a flat response at around the resonant wavelength.⁹ Using computational tools, we examined the dependence of resonance condition on the magnitude and phase properties of the top mirror. In order to obtain a flat-top, we need a top mirror with a modified reflectivity with a dip in the reflectivity at the resonant wavelength. In Fig. 7, we plot the quantum efficiency of a detector with the modified top-mirror and a detector with no mirror structure on top exhibiting near-unity efficiency at resonance wavelength. A factor of 3 improvement in the width of the peak spectral response is evident in this graph at 90% of the peak efficiency.

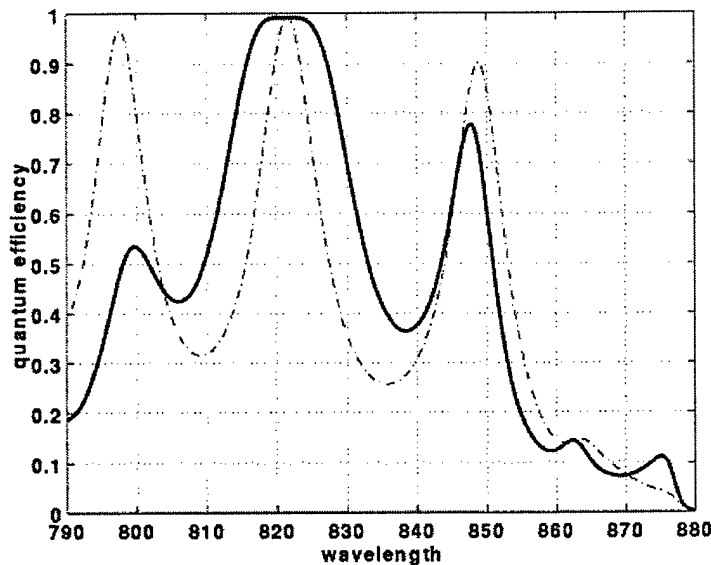


Fig. 7. The calculated quantum efficiencies of a near-unity efficiency RCE detector with (solid) and without (dashed) the modified top mirror

5. Vertical Cavity Polarization Detector Arrays for Polarization Imaging

A novel device architecture that detects not only light but also its polarization could substantially reduce the number of optical components in a range of systems. Image sensors built with the devices would represent an essentially new type of optical component. Sensitivity to polarization of light is similar to full-color imaging, where the eye can pick out details against a background based on color differences. A range of new applications may exist for a compact polarization imager, where the polarization of light reveals more information than humans can directly perceive.

The RCE detectors are inherently sensitive to polarization of light and such detector pairs can serve as polarization sensors.¹⁰ The proposed device structure consists of a RCE photodiode vertically integrated with a conventional detector, creating a single device that is differentially polarization of light. The resulting vertical cavity polarization detector (VCPD) is constructed so that the top resonant cavity traps photons with a large electric vector normal to the surface while transmitting photons with a large normal magnetic vector to the bottom detector (Fig.8).¹¹ Thus, the combined detectors register a differential response depending on the polarization of the light striking the top surface. During the fabrication process, a Bragg reflector bottom mirror and reflection from the top silicon air interface form a resonant cavity photodiode. The bottom part of the structure is another Si detector fabricated with standard photolithography ion implantation and metalization processes. The big advantage to this kind of structure is that light is illuminating one mesa and alignment is not critical.

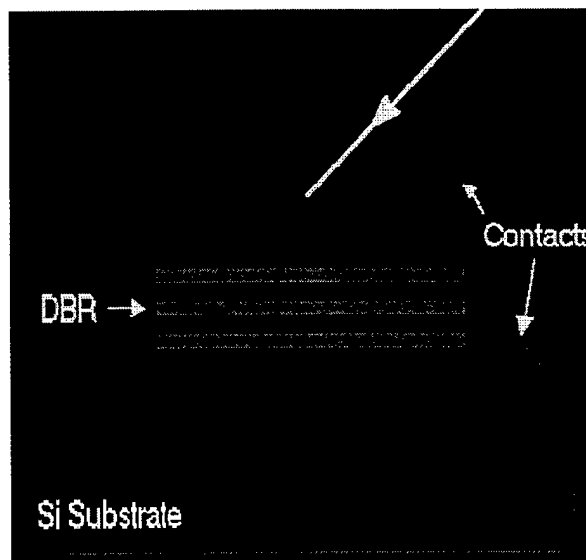


Fig. 8. Schematic representation of the proposed VCPD structure.

We considered Si for the specific application of magneto-optical drives the wavelength of light is about 650 nm. For that wavelength of light, the absorption coefficient of silicon is almost ideal for the application. We have

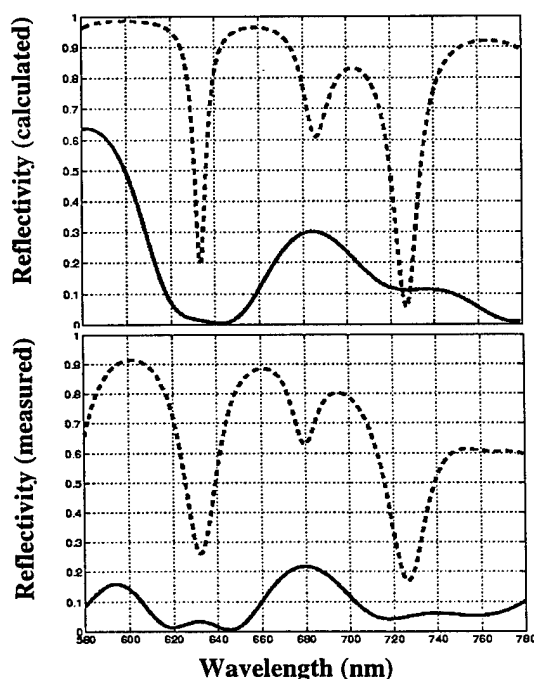


Fig.10. Theoretical (top) and measured (bottom) reflectivity of the VCPD structure of Fig.9.

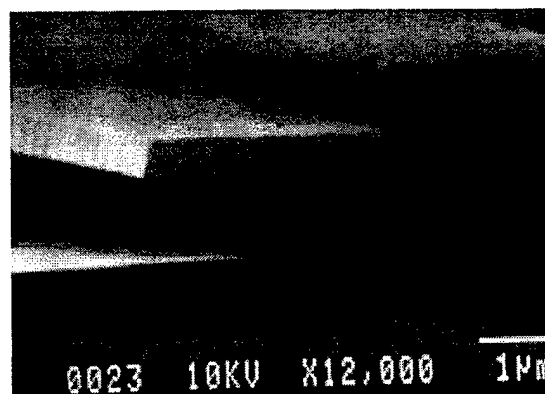


Fig.9. SEM photograph of a LPCVD grown Si/SiO₂/Si₃N₄ VCPD structure.

fabricated Si VCPD structures using LPCVD for the growth of DBR and top Si detector layers (see Fig.9 for an SEM photograph of the fabricated structure).

Figure 10 shows the comparison of theoretical and measured reflectivities for the Si/SiO₂/Si₃N₄ VCPD designed for 632 nm wavelength demonstrating the feasibility of fabricating devices with prescribed optical properties. Due

to the difficulties, mostly related to the inadequacy of the fabrication facility, we were unable to obtain the expected electrical performance of these devices.

6. Publications

In addition to the journal papers referenced in the discussion of the results above, we have recently submitted another article on light emission in Si APDs.¹² We have also published a number of conference papers.¹³ Two students (Bora Onat and Olufemi Dosunmu) have received their MS degrees in EE, Bora Onat have completed his PhD in EE (now working at Lucent) and two other students (Gökkavas, EE and Ulu, Physics) are now in the final year of their PhD work.

REFERENCES

- ¹ M. S. Ünlü and S. Strite *J. Appl. Phys.* **78**, pp. 607-628, 1995.
- ² E. Özbay, S. Islam, B. M. Onat, M. Gökkavas, O. Aytür, G. Tuttle, E. Towe, R. H. Henderson, and M. S. Ünlü, "Fabrication of High Speed Resonant Cavity Enhanced Schottky Photodiodes," *IEEE Photon Technol. Lett.*, vol. 9, pp. 672 - 674, 1997.
- ³ B. M. Onat, M. Gökkavas, E. Özbay, E. Ata, E. Towe, and M. S. Ünlü, "100 GHz Resonant Cavity Enhanced Schottky Photodiodes," *IEEE Photon Technol. Lett.*, vol.10, pp. 707-709, 1998.
- ⁴ M. S. Ünlü, M. Gökkavas, B. M. Onat, E. Özbay, R. P. Mirin, K. J. Knopp, K. A. Bertness, and D. H. Christensen, "High Bandwidth-efficiency Resonant Cavity Enhanced Schottky Photodiodes for 800-850 nm Wavelength Operation," *Applied Physics Letters*, vol. 72, no. 21, pp. 2727-2729, 1998.
- ⁵ M. Gökkavas, B. M. Onat, E. Özbay, E. P. Ata, J. Xu, E. Towe, and M. S. Ünlü, "Design and Optimization of High-Speed Resonant Cavity Enhanced Schottky Photodiodes," *IEEE J. Quantum Electron.*, vol. 35, no. 2, pp. 208-215, 1999.
- ⁶ E. Özbay, I. Kimukin, N. Biyikili, O. Aytür, M. Gökkavas, G. Ulu, R. P. Mirin, K. A. Bertness, D. H. Christensen, and M. S. Ünlü, "High Speed > 90% Quantum-Efficiency p-i-n Photodiodes with a Resonance Wavelength Adjustable in 795-835 nm Range," *Applied Physics Letters*, vol. 74, no. 8, pp. 1074-1076, 1999.
- ⁷ G. Ulu, M. Gökkavas, M. S. Ünlü, N. Biyikli, I. Kimukin, E. Özbay, R. P. Mirin, K.A. Bertness, and D. H. Christensen, "High Speed Resonant Cavity Enhanced Photodiodes with Near-Unity Quantum Efficiency," *Trends in Optics Series, Ultrafast Electronics and Optoelectronics*, vol. 28, pp. 115-122, 1999.
- ⁸ M. S. Ünlü, E. Özbay, R. P. Mirin, D. H. Christensen, and E. Towe, "High Speed Resonant Cavity Enhanced Photodiodes," *Optics and Photonics News*, December 1999.
- ⁹ M. Gökkavas, G. Ulu, and M. S. Ünlü, "Resonant Cavity Enhanced Photodiodes with a Flat Spectral Response," *Trends in Optics Series, Ultrafast Electronics and Optoelectronics*, vol. 28, pp. 208, 1999.

¹⁰ M. S. Ünlü and H. P. Zengingönül, "Polarization Sensing with Resonant Cavity Enhanced Photodetector Pairs," *Electron. Lett.*, vol. 32, no. 6, pp. 593 - 595, 1996.

¹¹ B. M. Onat and M. S. Ünlü, "Polarization Sensing with Resonant Cavity Enhanced Photodetectors," *IEEE J. Selected Topics in Quantum Electron.*, vol. 2, no. 1, pp. 135 - 140, 1996.

¹² G. Ulu, A. V. Sergienko, and M. S. Ünlü, "Influence of hot carrier luminescence from avalanche photodiodes on time correlated photon counting," *OSA Optics Letters*, pending., 2000.

¹³ **Conference Papers published under ONR funding:**

M. S. Ünlü, Mutlu Gökkavas, G. Ulu, R. P. Mirin, and D. Christensen, "High-Speed, High-Efficiency Photodetectors for Short Pulse Applications", November 1999.

G. Ulu, A. V. Sergienko, and M. S. Ünlü, "Absolute Calibration of Analog and Photon Counting Detectors using Entangled Photons", *Bulletin of APS centennial meeting.*, March 1999.

E. Özbay, R. P. Mirin, D. H. Christensen, and M. S. Ünlü, "High-Speed Resonant Cavity Enhanced Photodetectors", January 1999.

G. Ulu, M. Gökkavas, M. S. Ünlü, N. Biyikli, E. Özbay, R. P. Mirin, and D. H. Christensen, "Near-Unity Quantum Efficiency High Speed p-i-n Photodiodes", *Proceedings of SPIE, Photodetectors: Material and Devices*, January 1999.

B. M. Onat, G. Ulu, and M. S. Ünlü, "Polarization Sensing Photodetectors", *Proceedings of SPIE Optoelectronic Integrated Circuits II*, Vol. 3290, 1998.

B. M. Onat and M. S. Ünlü, "Polarization Sensing with Resonant Cavity Enhanced Photodetectors", *Proceedings of IEEE LEOS'96 Annual Meeting*, November 18 - 21 1996.

G. Ulu, M. Gökkavas, M. S. Ünlü, N. Biyikli, E. Özbay, R. P. Mirin, and D. H. Christensen, "Near-Unity Quantum Efficiency High Speed p-i-n Photodiodes", *Proceedings of SPIE, Photodetectors: Material and Devices*, January 1999.

M. S. Ünlü, B. M. Onat, M. Gökkavas, E. Özbay, E. P. Ata, E. Towe, G. Tuttle, K. Bertness, K. Knopp, R. Mirin, and D. Christensen, "Ultrafast Resonant Cavity Enhanced Schottky Photodiodes", *Proceedings of SPIE Optoelectronic Integrated Circuits II*, 1998.

M. Gökkavas, B. M. Onat, E. Özbay, M. S. Islam, E. P. Ata, E. Towe, G. Tuttle, and M. S. Ünlü, "Ultrafast Resonant Cavity Enhanced Schottky Photodiodes", *Proceedings of IEEE LEOS'97 Annual Meeting*, November 10 -13 1997.

M. S. Ünlü, "High-Speed Resonant Cavity Enhanced Schottky Photodiodes", *Proc. of Int'l Semiconductor Device Research Symposium*, Charlottesville, December 1997.

E. P. Ata, M. Gökkavas, B. M. Onat, M. S. Islam, G. Tuttle, R. Mirin, K. J. Knopp, K. A. Bertness, D. H. Christensen, M. S. Ünlü, and E. Özbay, "High Bandwidth-Efficiency GaAs Schottky Photodiodes for 840 nm Operation Wavelength", *Proc. of Int'l Semiconductor Device Research Symp.*, December 1997.

S. Islam, E. Özbay, O. Aytür, B. M. Onat, M. Gökkavas, and M. S. Ünlü, "Fabrication of High-Speed Resonant Cavity Enhanced Schottky Photodiodes", OSA Spring Topical Meeting on Ultrafast Electronics and Optoelectronics, 1997.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE	3. REPORT TYPE AND DATES COVERED Final Report June 96 - August 99	
4. TITLE AND SUBTITLE High-Performance Ultrafast Photodetectors			5. FUNDING NUMBERS N00014-96-1-0652	
6. AUTHOR(S) M. Selim Ünlü				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Boston University 881 Commonwealth Avenue Boston, MA 02215			8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research 800 North Quincy Street Arlington, VA 22117-5660			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Public release, no limitations for distribution			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) This project concentrates on the design, fabrication and characterization of compound semiconductor photodetectors in various material systems operating at near-IR wavelengths. We utilize resonant cavity enhanced (RCE) detection scheme to optimize speed and responsivity of photodetectors. It is also desirable to combine multiple functions in a single photodetector structure. In addition to wavelength selectivity of RCE photodetectors, we have demonstrated that RCE detectors vertically integrated with one-pass detectors can be used for polarization sensing. We have fabricated RCE photodetectors working at 800 to 900 nm wavelength range with record bandwidth-efficiency products. RCE Schottky photodiodes with 100 GHz bandwidth, p-i-n photodiodes with 50GHz bandwidth and near-unity quantum efficiency have been demonstrated.				
14. SUBJECT TERMS Photodetectors, high-speed, high-efficiency, resonant cavity			15. NUMBER OF PAGES	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT	20. LIMITATION OF ABSTRACT	

NSN 7540-01-280-5500

DTIC QUALITY INSPECTED 3

Standard Form 298 (Rev. 2-89)
Prescribed by ANSI Std. Z39-18
298-102

ENC 11