

ARMY RESEARCH LABORATORY



Role of Oxide Additives in Stabilizing Zirconia for Coating Applications

by Jeffrey J. Swab

ARL-TR-2591

September 2001

Approved for public release; distribution is unlimited.

20011128 070

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

Army Research Laboratory

Aberdeen Proving Ground, MD 21005-5069

ARL-TR-2591

September 2001

Role of Oxide Additives in Stabilizing Zirconia for Coating Applications

Jeffrey J. Swab

Weapons and Materials Research Directorate, ARL

Approved for public release; distribution is unlimited.

Abstract

Zirconium dioxide (ZrO_2) is a ceramic with a variety of industrial applications as a refractory material, and it is used in electronic packaging, biomedicine, and advanced engines. Unfortunately, pure zirconia undergoes a destructive phase transformation that severely limits its uses. However, some oxide additives have been found to control this transformation and ultimately lead to significant improvements in the material. This report summarizes the role that oxide additives play in controlling these transformations, and the resulting applications of ZrO_2 -based coatings are discussed.

Table of Contents

		<u>Page</u>
	List of Figures	v
	List of Tables	v
1.	Introduction	1
2.	Zirconia Overview	1
2.1	Phases.....	1
2.2	Phase Transformations.....	2
3.	Oxide Additives as Phase Stabilizers	3
3.1	Selecting an Oxide Additive	3
3.2	Phase Relations in ZrO ₂ /Oxide Binary Systems	4
3.2.1	<i>MgO-ZrO₂</i>	4
3.2.2	<i>CaO-ZrO₂</i>	5
3.2.3	<i>Y₂O₃-ZrO₂</i>	6
3.2.4	<i>CeO₂-ZrO₂</i>	9
3.2.5	<i>Other Rare-Earth Oxide-ZrO₂</i>	9
3.3	Microstructures in ZrO ₂ /Oxide Binary Systems	12
3.3.1	<i>Partially Stabilized Zirconia (PSZ)</i>	12
3.3.2	<i>Tetragonal Zirconia Polycrystals (TZP)</i>	12
3.3.3	<i>Zirconia-Toughened Ceramics (ZTC)</i>	13
4.	Aspects of Toughening by ZrO₂	13
4.1	Nucleation of Martensitic Transformations	14
4.2	Effect of Particle Size	14
4.3	Toughening Mechanisms in ZrO ₂ Systems.....	15
4.3.1	<i>Transformation Toughening</i>	15
4.3.2	<i>Microcrack Toughening</i>	16
4.3.3	<i>Crack Deflection</i>	16
5.	Developing ZrO₂ Coatings	17
5.1	Coating Deposition	17
5.2	Thermal Barrier Coatings.....	18
5.3	Environmental Barrier Coatings	19

	<u>Page</u>
5.3.1 <i>Interaction of ZrO₂ and Typical Corrosive Media</i>	20
5.3.2 <i>Interaction of Zirconia and Its Stabilizing Oxides With Sulfur Compounds</i>	20
5.3.3 <i>Interaction of ZrO₂ and Its Stabilizing Oxides With Vanadium Compounds</i>	21
5.3.4 <i>Scandium and Indium Oxides as Hot-Corrosion-Resistant Stabilizers for ZrO₂</i>	22
6. Summary	23
7. References	25
Distribution List	31
Report Documentation Page	33

List of Figures

<u>Figure</u>	<u>Page</u>
1. ZrO ₂ -Rich End of the MgO-ZrO ₂ Phase Diagram	5
2. ZrO ₂ -CaO Phase Diagram	6
3. Low Y ₂ O ₃ Region of the Y ₂ O ₃ -ZrO ₂ Phase Diagram	7
4. Low CeO ₂ Region of the CeO ₂ -ZrO ₂ Phase Diagram	10

List of Tables

<u>Table</u>	<u>Page</u>
1. Reaction Behavior and Products for Ceramic Oxide-Vanadium Compounds	22

INTENTIONALLY LEFT BLANK.

1. Introduction

Zirconium dioxide (ZrO_2) is a versatile ceramic material. Its high melting point (2,680 °C) makes it an ideal refractory material, and initially this was the extent of its industrial applications. Over the past several decades, however, significant advances have been made in understanding the processing/structure/properties relationships of zirconia. Extensive research was conducted on zirconia-based systems in the 1980s. In fact, during this time, there were three conferences specifically devoted to the science and technology of zirconia [1–3]. An advanced understanding of zirconia has led to its application as an oxygen sensor, thermally insulative and corrosion-resistant coating for advanced engines, a joint replacement material for human hips, and a variety of other high-temperature structural and wear applications.

Pure ZrO_2 has severely limited applications due to a destructive tetragonal-to-monoclinic phase transformation. Fortunately, adding various oxides controls and enables the manipulation of this phase transformation. Through careful processing and compositional engineering, zirconia-based systems have been developed to satisfy the demands of many specialty applications. This report discusses the thermodynamic role of these oxide stabilizers in controlling the inherent phase transformations in ZrO_2 and the application of ZrO_2 coatings.

2. Zirconia Overview

2.1 Phases. Zirconia undergoes the following three solid polymorphic phase changes at atmospheric pressure:



The cubic (c-) phase, which is stable from 2,370 °C to the melting point, has a fluorite-type structure with each Zr atom octahedrally coordinated with eight oxygen atoms, all at an equal distance. Oxygen atoms are tetrahedrally coordinated to four equidistant Zr atoms. The

tetragonal (t-) phase is stable below 2,370 °C to approximately 1,170 °C. In this phase, the Zr atoms continue to be octahedrally coordinated to the oxygen atoms, but the eight oxygen atoms are no longer equidistant. Instead, four are approximately 15% closer to the Zr atoms than the other four oxygen atoms. This phase has a distorted crystal structure which is termed face-centered tetragonal. Monoclinic (m-) ZrO₂ is stable at all temperatures below approximately 1,170°C. This is the naturally occurring mineral form of zirconia, baddeleyite, that also has a distorted tetragonal crystal structure. This phase is unique in that the Zr atoms have a sevenfold coordination with the oxygen at varying bond lengths and angles.

2.2 Phase Transformations. Pure ZrO₂ undergoes two phase transformations after it cools from near the melting point to room temperature: (1) cubic to tetragonal (c → t), at approximately 2,370 °C and (2) tetragonal to monoclinic (t → m) around 1,170 °C. In both cases, the driving force for the transformation is so high (free energy of the t-phase [G_t] >> the free energy of the c-phase [G_c] in the former, and the free energy of the m-phase [G_m] >> G_t in the latter transformation) that it is thermodynamically impossible to retain either the c- or t-phase at room temperature, even with rapid quenching. The t → m transformation is associated with a large crystallographic volume change which, even in small grains of pure ZrO₂, exceeds the elastic and fracture limits of the material and can only be accommodated by cracking and fracturing bulk pieces. This is the reason that large pieces of pure ZrO₂ cannot be successfully manufactured.

Both of these transformations are diffusionless and have been termed “martensitic” since they are analogous to classic martensitic transformations that are common in many hardened steel systems. Although the control of both inherent phase transformations is of interest, the t ↔ m transformation has the greatest implications on the industrial application of zirconia and has thus been studied extensively. This transformation has five distinct features:

- (1) It is a diffusionless transformation in which the atoms retain their neighbors in either phase, and the atomic movements are small, occurring mainly with the oxygen atoms.

- (2) It involves a large shear strain ($\approx 8\%$) and significant volume change (3–5%).
- (3) It exhibits a thermal hysteresis, with the forward transformation occurring around 1,170 °C and the reverse between 600 °C and 1,000 °C.
- (4) The t-phase cannot be retained at room temperature, even with rapid quenching.
- (5) The transformation is athermal (i.e., the amount of the transformed phase changes by varying the temperature, but not as a function of time at temperature).

A variety of oxide additives can successfully retain the c- and/or t-phase metastably at room temperature. In 1975, Garvie et al. [4] first proposed that the volume expansion associated with $t \rightarrow m$ transformation could be beneficial in improving both the toughness and strength of ceramics. In these materials, the t-phase is retained metastably at room temperature by adding an oxide. The oxide acts to “stabilize” the ZrO_2 structure by decreasing the transformation ΔG and making it possible to retain the t-phase metastably at room temperature, avoiding the deleterious volume change.

The following sections will discuss the role of various oxides in the stabilization process, the resultant structure and properties of these materials, and the development of zirconia coatings.

3. Oxide Additives as Phase Stabilizers

3.1 Selecting an Oxide Additive. It has been known for years that adding certain oxides to ZrO_2 will stabilize ZrO_2 against its inherent phase transformations. Though the mechanisms by which these oxides serve to stabilize ZrO_2 have been studied, there is still a lot to understand, and discussions continue as to the actual mechanisms. Research has, however, led to the agreement of some general criteria for selecting stabilizing oxides. These four criteria are: 1) the cation radii should be close to that of Zr^{+4} (0.084 nm) to minimize lattice distortions which can lead to

high shear stresses and spontaneous transformations; 2) the cation should have a stable +2 or +3 state, which, when added to the ZrO_2 , will produce oxygen vacancies; 3) the oxide crystal structure should be cubic or tetragonal, depending on the ZrO_2 phase to be stabilized; and 4) the oxide should have some degree of solubility in ZrO_2 , with a higher solubility preferred. These rules hold quite well. The one known exception to this, CeO_2 (Ce^{+4}), is an excellent stabilizing oxide, even though oxygen vacancies are not developed. The traditional oxide additives that have been used are MgO [5–7], CaO [7–9], and Y_2O_3 [10–12]. A variety of commercial products based on ZrO_2 have been produced using these additives. More recently, CeO_2 [13–14] and other rare-earth oxides [15–20] have also been shown to stabilize ZrO_2 to varying degrees. However, a major limitation to commercializing these rare-earth stabilized zirconias is the high cost of the oxide additive.

3.2 Phase Relations in ZrO_2 /Oxide Binary Systems. The amount of added oxide, as well as its solubility in ZrO_2 , will determine the extent of stabilization and which phase and/or phases can be retained at room temperature. This section will review the binary phase diagrams of ZrO_2 with the most common oxide stabilizers, as well as some of the newer rare-earth oxides.

3.2.1 $MgO-ZrO_2$. There is still a lot of discussion on the exact phase diagram for the $MgO-ZrO_2$ system, but the generally accepted diagram [6] is shown in Figure 1. In this system, there is little or no solubility of MgO in $m-ZrO_2$. Between 1,240 °C and 1,400 °C, the solubility increases slightly to around 1 mole-percent in a tetragonal solid solution field. Above this temperature range, a large cubic solid solution field is present with a eutectoid composition at 13 mole-percent MgO . At this eutectoid composition, fully-stabilized cubic ZrO_2 can be easily retained to room temperature with appropriate cooling. Most commercial materials are produced with a MgO content between 8 and 10 mole-percent, which results in a product with both c- and t-phases. It is beneficial to retain the t-phase since it can transform to the m-phase with the associated volume change and enhance the material's strength and toughness. This type of material is labeled as a partially-stabilized zirconia (PSZ) [6]. At higher MgO contents, with the c-phase being predominant, the material is considered a fully-stabilized zirconia (FSZ).

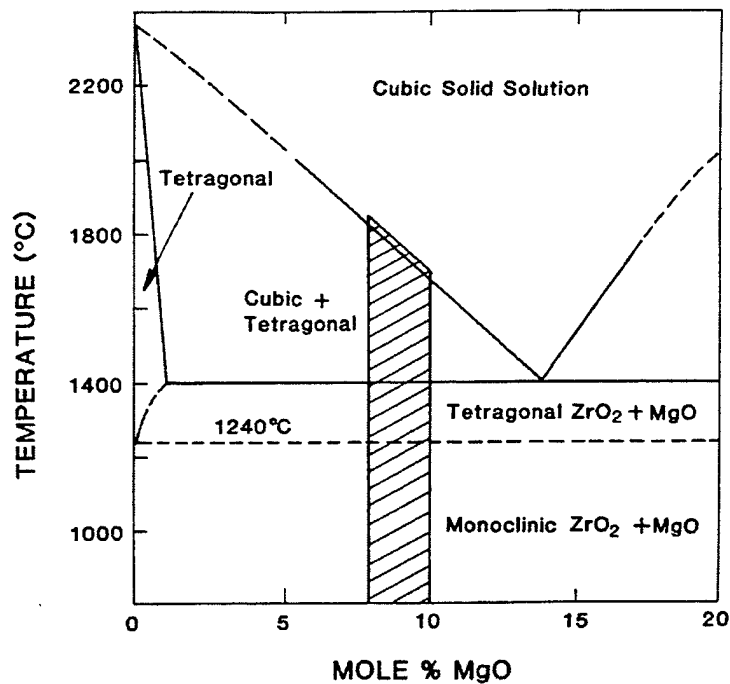


Figure 1. ZrO₂-Rich End of the MgO-ZrO₂ Phase Diagram [6].

Another feature of this system is the decomposition of the cubic solid solution to the other phases upon cooling. During decomposition, it is thought that the MgO leaves the ZrO₂ and migrates along grain boundaries and to intergranular voids. The resultant ZrO₂, no longer properly stabilized, has inferior properties limiting its high temperature applications. Materials with low MgO content are very susceptible to large losses in strength and toughness when exposed to elevated temperatures (~1,000 °C) for long periods of time (>1,000 hr) [21]. This “overaging” severely limits the high temperature applicability of this material.

3.2.2 CaO-ZrO₂. As with the MgO-ZrO₂ system, there is confusion about which phases are present, their compositions, and the eutectoid temperature. The most recent phase diagram is presented in Figure 2 [22]. Unlike the MgO-ZrO₂ system, CaO does exhibit solubility, albeit limited, in the m-phase below 1,000 °C. At this low CaO content, increasing the temperature

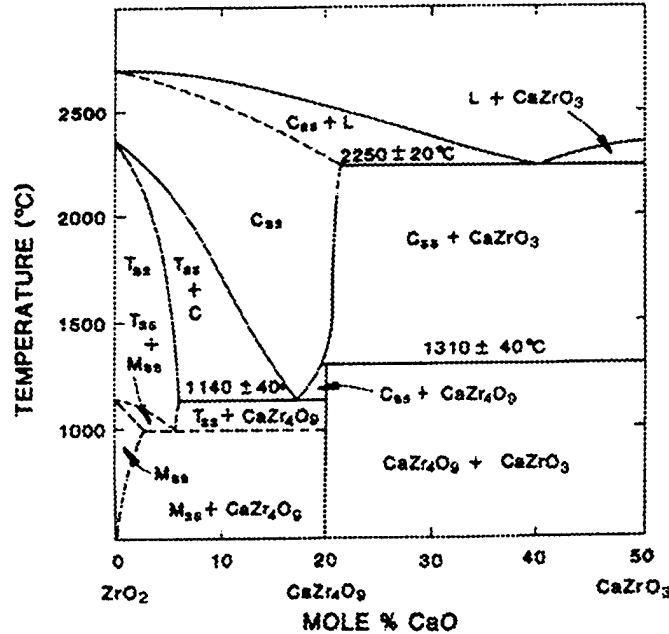


Figure 2. ZrO_2 -CaO Phase Diagram [22].

results in a shift to a t-phase plus m-phase solid solution field with further temperature increases leading to a tetragonal solid solution field.

Above 1,140 °C, with increasing CaO content, a two-phase region of tetragonal and cubic solid solution exists, and with further increases in CaO to ~20 mole-percent, a cubic solid solution phase exists. Slow cooling through the eutectoid at 1,140 °C at 17 mole-percent CaO results in a region with a tetragonal solid solution and a decomposition product. Both PSZ and FSZ materials can be produced in this system. However, the high temperature engineering applications of CaO-PSZ are limited because studies have shown that “aging” (time at temperature [>800 °C]) results in microstructural changes that degrade the properties of the material [23].

3.2.3 Y_2O_3 - ZrO_2 Examining the low Y_2O_3 region of the Y_2O_3 - ZrO_2 phase diagram, shown in Figure 3 [10], reveals two distinct differences between this system and the two previously discussed. First, the tetragonal solid solution field is much larger; secondly, the $t \rightarrow m$

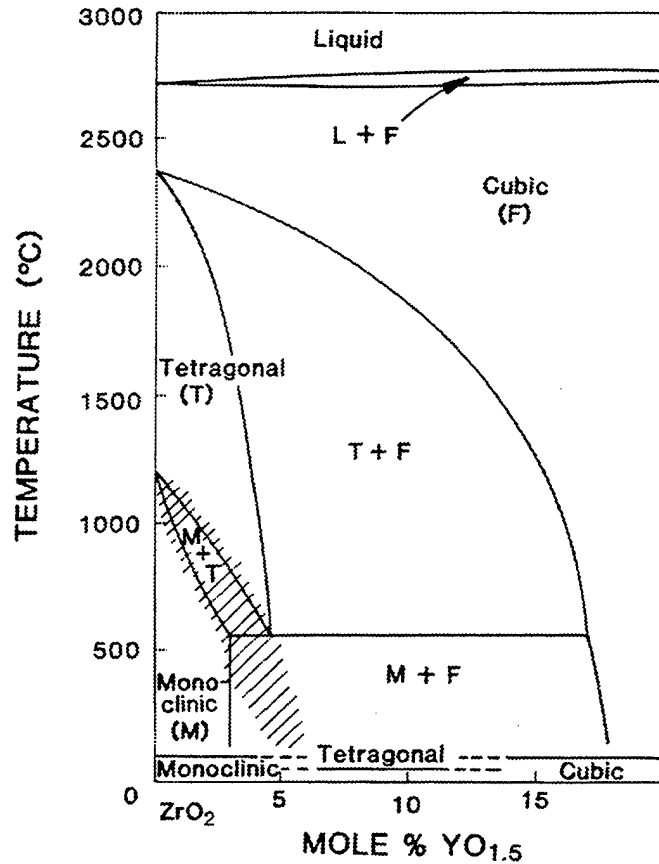


Figure 3. Low Y_2O_3 Region of the $\text{Y}_2\text{O}_3\text{-ZrO}_2$ Phase Diagram [10].

transformation temperature is significantly lower. These two features enable the production of ZrO_2 ceramics that are essentially 100% tetragonal phase with significantly improved strength and fracture toughness. These materials have been labeled as TZPs—tetragonal zirconia polycrystals.

Other features of this system are that two types of t- ZrO_2 can be developed. At Y_2O_3 contents of approximately 4 mole-percent or less with increasing temperatures, a “transformable” t-phase field is encountered. This t-phase will transform to the m-phase on cooling. At Y_2O_3 contents above 4 mole-percent, a mixture of c-phase and an “untransformable” t-phase, labeled as t'-phase, can be displacively created.

Because of the enhanced strength and toughness of ZrO_2 with Y_2O_3 contents between 2 and 4 mole-percent, the material has been examined for high-temperature structural applications, such as engine components [21, 24, 25]. Further additions of Y_2O_3 create a homogeneous c-phase that is stable from room temperature to the melting point.

One drawback of this system is a well-documented, low-temperature aging phenomenon when the Y_2O_3 content is below 4 mole-percent. At temperatures between 200 °C and 300 °C, and in the presence of water vapor, this material can undergo a catastrophic microcracking that can turn a bulk piece of Y_2O_3 - ZrO_2 to rubble [26–29]. Materials surviving intact have extensive microcracking that significantly reduces the properties and makes the material essentially useless.

There are many theories as to the cause of this phenomenon. Sato et al. [27] have proposed a theory where Zr-OH bonds are formed when water reacts with Zr-O-Zr bonds at the crack tip. They showed that in addition to aqueous solutions, certain nonaqueous solutions with a lone-pair electron orbital opposite a proton donor site enhance the rate of transformation at low temperatures. It was concluded that under these conditions, the strain that acts to stabilize the t-phase is released. This, coupled with the growth of pre-existing flaws, accelerates the transformation. The hypotheses of Yoshimura et al. [30–31] is similar in that it is also based on the formation of Zr-OH bonds, but they suggest a four-step degradation process. The H_2O is absorbed onto the Y-TZP surface and dissociates, forming Zr-OH bonds which create stress sites. These sites build as the OH^- ions diffuse through the surface and the lattice, resulting in “nucleation” sites for the phase transformation. When the stress level reaches a critical level, the $t \rightarrow m$ transformation will occur with its associated cracking, enabling the process to continue. Their assumptions are based on findings which show that a transformed m- ZrO_2 had an OH group not found attached to untransformed t- ZrO_2 . Adding OH to the m-phase increases the lattice parameter, which can be returned to its original value if the specimen is dried.

Lange et al. [32] have seen the formation of 20–50 nm crystallites of $\alpha\text{-Y}(\text{OH})_3$, and they proposed that the formation of this hydroxide draws the yttria from the t-grains on the surface, creating monoclinic nuclei. As yttria depletion continues, these nuclei grow until a critical size is reached where they can spontaneously transform. If the transformed grains are large enough, microcracking will occur. The microcracking provides an avenue for the water to penetrate below the surface, which allows the process to continue. If the transformed grains are smaller than the critical size necessary for microcracking, the transformation and subsequent degradation will be limited by the long-range diffusion of Y_2O_3 to the surface. Auger electron spectroscopy has shown a homogeneous, yttrium-rich surface layer on specimens after only 5 hr of exposure to 177 °C in a nitrogen environment [33]. This supports the theory of Lange et al. [32].

At low Y_2O_3 levels, the grain size is critical. Lange reported that retaining the t-phase during processing depends on a combination of grain size and yttria content [34]. A critical grain size (D_c) for retaining >90% of the t-phase can be defined by plotting the grain size vs. mole-percent yttria. The general trend is that as the amount of yttria is decreased, so must D_c . For a given yttria content above D_c , the retaining the t-phase becomes increasingly difficult. The same relationship seems to apply to this low-temperature degradation phenomenon [29], which has led to the investigation of CeO_2 and other rare-earth oxides as alternate stabilizers for ZrO_2 .

3.2.4 $\text{CeO}_2\text{-ZrO}_2$ Like the $\text{Y}_2\text{O}_3\text{-ZrO}_2$ system, this binary system exhibits an extensive tetragonal solid solution phase field, as shown in Figure 4 [35], giving rise to the formation of a TZP material. Unfortunately, the strength of this material is inferior to its Y_2O_3 counterpart because the grain size is significantly larger. Although the commercial applications do not match those of the $\text{Y}_2\text{O}_3\text{-ZrO}_2$ material, plasma-sprayed CeO_2 -stabilized ZrO_2 has been patented as a corrosion-resistant coating for superalloys [36].

3.2.5 Other Rare-Earth Oxide- ZrO_2 There have been several studies to examine other rare-earth oxides as stabilizers for ZrO_2 [15–20]. Unfortunately, little research has focused on developing phase diagrams for these systems or on the resultant properties, so there are many questions yet to be answered.

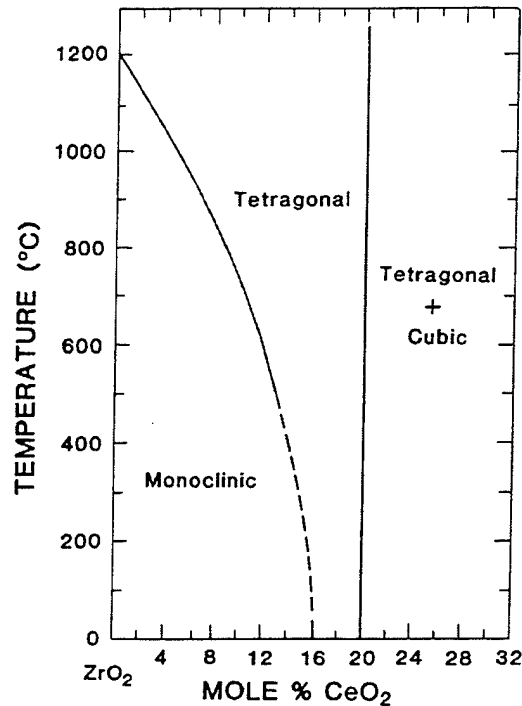


Figure 4. Low CeO₂ Region of the CeO₂-ZrO₂ Phase Diagram [30].

Several of the studies [15–17] have examined mixtures of many of these oxides [17], or have added or partially substituted a second oxide in a Y₂O₃- [15–16] or CeO₂-ZrO₂ [15] system. There have been some interesting results. Pyda et al. [17] used a mixture that primarily contained CeO₂, Ln₂O₃, and Nd₂O₃, plus minor amounts of many other rare-earth oxides. They were able to obtain a fine-grained TZP material with a 5–7 mole-percent of the oxide mixture. When 3 mole-percent or more of the oxide mixture was used, chemical segregation occurred. Two ordered phases, Ln₂Zr₂O₇ and Ce₂Zr₃O₁₀, coexist with the t-phase, and the amount of these phases increases with increasing stabilizer content.

Duh et al. [15] used a 12 mole-percent CeO₂-ZrO₂ system as their base material. They found that replacing 2 mole-percent of the CeO₂ with Y₂O₃, Sm₂O₃, Nd₂O₃ or Dy₂O₃ resulted in a finer-grained material that was essentially all t-phase, but there was a significant decrease in fracture toughness. They proposed that reduced fracture toughness was due to either reduced free energy

of the t-phase, or an increase in the constraint on the t-grains, preventing transformation. One unmentioned possibility was that these substitutions might result a nontransformable t-phase.

Log et al. [18] attempted to produce ZrO_2 material using 3 mole-percent of a variety of rare-earth oxides in place of Y_2O_3 . The purpose was to lower the annealing temperatures for a displacively formed t'-phase. They fabricated polycrystalline t'- ZrO_2 using Dy_2O_3 , Er_2O_3 , and Yb_2O_3 . The material had toughness values significantly higher than c- ZrO_2 , but the strength was severely reduced by the large grain size.

Another study investigating the development of zirconia fibers by sol-gel processing added different concentrations of a variety of rare-earth oxides [19]. The large cation radius of Ln, Pr, and Nd yielded t- ZrO_2 when calcined at 900 °C, but yielded partly or fully m- ZrO_2 with or without a cubic zirconia phosphate phase at higher temperatures. The smaller cation radius of Sm, Gd, and Dy yielded only t- ZrO_2 and c- ZrO_2 , or a combination of these two phases. The crystallite size, lattice strain, and tensile strength were also affected by this difference in cation size.

Duran [20] produced a phase diagram for the Er_2O_3 - ZrO_2 binary system using high-temperature x-ray diffraction and thermal expansion measurements. He showed that erbia could indeed stabilize ZrO_2 , but the effect on the properties of the resultant materials was not reported.

Jones [37–39] investigated other oxides for stabilizing ZrO_2 for corrosion-resistant thermal barrier coatings (TBC) in engine applications. Sc_2O_3 and In_2O_3 have been examined because Y_2O_3 can be effectively leached from the ZrO_2 by some fuel impurities, resulting in the degradation of TBC. The phase relations in these systems have not been examined in great depth as part of these studies.

3.3 Microstructures in ZrO₂/Oxide Binary Systems. The most common, and thus most utilized microstructures that result from stabilizing ZrO₂ by adding an oxide are described in the next section.

3.3.1 Partially Stabilized Zirconia (PSZ). PSZ materials are generally developed by adding MgO, CaO, or Y₂O₃ at levels that will allow c-phase to be formed without completely stabilizing the c-phase. These materials are heated in the c-phase field and when cooled t-grains precipitate out. At room temperature, the metastable t-phase, lenticular in shape, is confined in the c-matrix. The cooling portion is critical to the properties of the final product. The aim of cooling is to uniformly distribute the t-grains, retain as many of the precipitated grains in the t-phase at room temperature as possible, and avoid the precipitation of the t-grains at the grain boundaries, which can lead to the spontaneous transformation to m-grains.

This coarse-grained microstructure (grains are typically between 25 and 75 μm) is achieved by first rapidly cooling to below 1000 °C to produce the t-phase precipitates confined in the c-grains. The martensitic start (Ms) temperature of the t-grains is below room temperature. If this rapid cooling is sustained far below 1000 °C, an “underaged” material will result; the size of the t-grains are so small that even under an applied stress they will not transform. Next, the t-grains must be coarsened to the critical size so that they will transform easily under an applied stress. If the coarsening is done for too long, the grains will grow beyond the critical size, the Ms temperature will be above room temperature, and the grains will spontaneously transform to the m-phase when cooled; this is termed “overaging.”

3.3.2 Tetragonal Zirconia Polycrystals (TZP). These are also partially stabilized zirconias, but the oxide additive and the resultant microstructure are quite different from the PSZ materials. TZPs are typically stabilized by adding Y₂O₃ or CeO₂ because the solubility of each in ZrO₂ is much greater than either MgO or CaO. This enables greater stability of the t-grains against the t → m transformation, allowing the production of a ZrO₂ which is essentially 100% tetragonal. The t-grains are faceted and fine grained (≈2 μm or less, depending on the firing time,

temperature, and oxide content). Rühle and Heuer [40] indicated that autocatalytic nucleation is important for enhancing toughness in this class of zirconias. That is, the stress created by the t-grains that transform is transferred to neighboring grains, causing further transformation; thus, a discrete area of monoclinic grains surrounding the propagating crack tip are formed.

3.3.3 Zirconia-Toughened Ceramics (ZTC). Another class of partially stabilized zirconia systems are those in which ZrO_2 is not the matrix material, but rather it is dispersed in the matrix to enhance toughness. These materials are commonly referred to as zirconia toughened ceramics (ZTC).

By far, the most common material is zirconia toughened alumina (ZTA). Initial efforts centered on adding unstabilized ZrO_2 to Al_2O_3 . Both t- and m-grains of ZrO_2 toughened Al_2O_3 through phase transformation and/or microcracking toughening. Toughening could only be achieved with less than a 20 volume-percent of unstabilized ZrO_2 . The volume content of ZrO_2 could be much higher if the ZrO_2 was partially stabilized. ZrO_2 , with small amounts (2–3 mole-percent) of Y_2O_3 (TZP type) were added to Al_2O_3 , resulting in significant improvements in strength and toughness [41, 42]. Other ZTC systems include zirconia toughened spinel [43] and mullite [44, 45]. Attempts have been made with varying degrees of success to combine ZrO_2 (in a variety of forms) with nonoxides such as Si_3N_4 [43, 46, 47], SiC [43, 48] and TiB_2 [49].

4. Aspects of Toughening by ZrO_2

Controlling and manipulating both transformations, especially the t→m transformation, has led to the development of a class of zirconia materials that are deemed “transformation toughened.” There are several subclasses of these materials, but in all cases, toughening occurs when the stress field in front of a propagating crack encounters a t-grain. If sufficiently large enough, this stress field can initiate the t → m transformation, thus increasing the material’s resistance to crack propagation. This section discusses some aspects of transformation toughening.

4.1 Nucleation of Martensitic Transformations. The kinetics of the $t \rightarrow m$ transformation in ZrO_2 are nucleation controlled and can be examined as a transformation in either an “unconfined” or a “confined” state. Single-crystal ZrO_2 is the best material for examining the nucleation in an unconfined state, but PSZs, TZPs, and zirconia toughened ceramics, such as ZTA, where the t -grains are confined, is of greater industrial importance. Early discussions focused on whether this transformation followed a classical or a nonclassical model. Nucleation of the martensitic transformation in steels is considered a classic heterogeneous transformation since specific defect sites, typically dislocation based, serve as the nuclei for transformation.

Heuer and Rühle [40, 50] determined that the transformation in a confined state follows a nonclassical model. In all cases (PSZ, TZP, and ZTC), nucleation is the same, irrespective of whether it occurs on cooling during production, or in the presence of a stress field at the crack tip. The lack of dislocations in PSZ and ZTA are their reason. Some dislocations have been observed in TZPs, but they typically do not act as nucleation sites. Instead, the nucleation sites are particle/matrix interfaces or grain boundaries that act as a stress concentrator. They believe that nucleation is always stress-assisted, and that the stresses are typically produced during precipitation. Additionally, elastic moduli and thermal expansion mismatches, as well as thermal expansion anisotropy and crack tip stress, contribute to the overall stress at these nucleation sites. Particle size plays an important role in the nucleation and transformation of the t -phase.

4.2 Effect of Particle Size. Particle and grain size is critical to retaining the t -phase at room temperature in either an unconfined or confined state. Lange [51] determined that for a given temperature, there is a critical grain size necessary to prevent a spontaneous $t \rightarrow m$ transformation during cooling. If the t -grains are below this critical size, the thermodynamic free energy for the transformation is high and few grains transform. However, when these grains are above the critical size, the free energy is lowered, and the t -grains can spontaneously transform. Finding the appropriate grain size is critical to applying the material and depends on the oxide additive, its content, and the production technique.

This critical size also applies to the transformation under an applied stress field, such as that in front of a propagating crack. For enhanced toughening, the ideal condition is for the t-grains to be a size just below the size necessary for spontaneous transformation. In PSZ materials, the size dependence is pronounced. The t-phase is present as coherent precipitates, with an oblate shape (which minimizes stresses), in a c-phase field. Proper “aging” (exposure to elevated temperatures) of PSZ can easily bring the precipitates to the edge of this critical size. It can also just as easily coarsen the grains beyond this critical size through “overaging,” resulting in a spontaneous transformation and the loss of toughening.

This is why TZP materials are of such interest. The fine-grained ($\leq 1 \mu\text{m}$), essentially 100% t-phase is significantly less likely to suffer from overaging. The grain size is well below the critical size, minimizing the likelihood of spontaneous transformation. The fine grain size also enhances the material’s strength. Unfortunately, this fine grain size can also have an adverse effect on the fracture toughness. If these grains are too small, few will transform, even in the presence of the crack tip stress field. Since the transformation is inhibited, there is minimal contribution from the transformation, resulting in a low fracture toughness.

4.3 Toughening Mechanisms in ZrO_2 Systems. In general, one of the major disadvantages of ceramics is that they are brittle—they have an inherent lack of toughness (resistance to crack propagation). Many attempts have been made, with varying degrees of success, to improve toughness in ceramics. These include compositional tailoring of the microstructure (in-situ toughening), or adding a second-phase material such as particulate, whiskers, fibers, or some combination. Many materials that are comprised of t-grains of ZrO_2 or contain these grains have toughness values higher than most ceramics. The $t \rightarrow m$ transformation is the reason for this enhancement. It is believed that there are three primary mechanisms: transformation toughening, microcrack toughening, and crack deflection [52, 53].

4.3.1 Transformation Toughening. This mechanism is a form of crack shielding. As a crack propagates, a zone of transformed grains develops in front of the crack tip. This zone reduces the stress at the crack tip, resulting in crack shielding and a resistance to crack extension.

If this zone not only extends in front of the crack tip, but also surrounds the crack (i.e., a wake), then a material may exhibit an R-curve effect (i.e., increasing toughness with increasing crack length). Many materials containing t-ZrO₂ exhibit this effect. This form of toughening is only expected when a wake develops during crack extension. In a material exhibiting an R-curve, it is easy for a small crack to propagate, and then the material becomes insensitive to the presence of large cracks.

4.3.2 Microcrack Toughening. This type of toughening occurs when an extending crack encounters a zone of microcracks. The microcracks significantly reduce the driving force for crack extension through crack bifurcation. Microcrack zones can arise in a material through localized residual stresses, which may be due to from thermal expansion, elastic modulus mismatches, or phase transformations. Low toughness grain boundaries may act as sites for developing such cracks. In materials comprised of or containing t-ZrO₂, microcracking may occur during fabrication since some t-grains transform during cooling. Controlling the amount of microcracking is critical, as zones of microcracks can act as stress concentrators and lead to a strength reduction. In terms of enhancing fracture toughness, the ideal case is to develop a material in which the t-grains are below the critical size necessary for spontaneous transformation, but in a range where it is possible to induce the development of a microcrack zone. A zone of microcracks may also form in front of a propagating crack because of the phase transformation. In this case, microcrack toughening can be considered a form of crack shielding.

4.3.3 Crack Deflection. In this mechanism, the crack is deflected out of a plane normal to the maximum tensile stress field. This can be accomplished by adding a second-phase material, or it can be caused by localized residual stresses. This mechanism is not as dominant in zirconia systems as are transformation or microcrack toughening, and it is not sensitive to temperature increases. This is an attractive way to produce materials that have fracture toughness values that are not temperature dependent.

5. Developing ZrO₂ Coatings

Materials based on ZrO₂ have been examined for a variety of industrial applications. Monolithic PSZ and TZP materials, with their high strength and toughness, were examined for gas turbine and diesel engine components. However, these materials have not been able to find a niche in engines because of reduced $t \rightarrow m$ driving force at elevated temperatures and the associated loss of properties and performance.

One area of the engine community in which zirconia is finding an application is as a thermally insulative coating (thermal barrier coating [TBC]), or as an environmental barrier coating (EBC). TBCs are used in many turbine engine applications to insulate a metallic component from high combustion temperatures; this leads to longer lifetimes for these components. An EBC the coating is designed to protect the metallic component from degradation due to corrosive media produced/ingested in the engine combustion cycle. In some cases, both thermal and environmental protection are necessary, and zirconia-based coatings are successfully being used to provide combined protection.

5.1 Coating Deposition. Zirconia coatings are typically deposited by a thermal spray process. Thermally deposited coatings are a cost-effective means of solving a variety of engineering problems. These types of coatings are most commonly applied to provide thermal insulation, improve wear, oxidation, or corrosion resistance, or to restore worn components. Thermal spraying is a term that describes a family of techniques that are used to deposit metallic or nonmetallic coatings onto prepared substrates. The spraying techniques (that are classified based on the heating source and the introduction of the coating material) include plasma, flame, wire arc, high-velocity oxyfuel (HVOF), and detonation gun. In all techniques, the coating material, in the form of a powder, rod, or wire, is melted by the heat source. Compressed air or a process gas accelerates a confined stream of these molten particles onto a substrate. On impact, the particles flatten, solidify, and form interlocking platelets that bond to the substrate. These techniques are similar to a welding, except that in welding the material is fused to the substrate

and stays attached through a metallurgical bond, while thermally sprayed coatings remain attached through a mechanical bond. Further details and information on the various thermal spray techniques can be obtained from references [54–57].

Plasma spraying is the preferred technique for depositing ZrO_2 -based coatings. In this technique, an electric arc is used to heat a gas or gas mixture to temperatures approaching 10,000 K. The gas ionizes creating a plasma. The powder is injected into this plasma and melted. The molten particles are then accelerated toward the substrate at speeds approaching Mach II velocities. The temperature and velocity of this plasma stream is controlled by the nozzle design, arc current, gas flow rate, and gas mixture ratio. Excellent coatings with high bond strength are produced by this method, and the process flexibility allows for producing coatings with varying density and porosity levels.

5.2 Thermal Barrier Coatings. TBCs are used in many turbine engine applications to insulate metallic components from high combustion temperatures leading in longer lifetimes for these components. Kvernes and Fartum [58] in Norway and Kamo and Bryzik [59] in the United States were some of the first to pioneer the use of plasma-sprayed ceramics in diesel engines. These coatings can be considered for application on the following diesel engine components: cylinder liners, piston caps, and valve faces. Almost all TBCs for engine applications are plasma-sprayed ZrO_2 -based materials. There are several reasons for using ZrO_2 -based materials. These coatings have extremely low thermal conductivity values (typically around 2 W/m K) that are significantly lower than the thermal conductivity of the metallic component. The powders of these materials are readily available and easy to deposit as a coating via a variety of thermal spraying techniques. A coating of 2 mm or less of this highly insulative ceramic can result in an increase in the component life by several orders of magnitude. Also, the coating is cheaper than the component it coats.

A joint effort between the U.S. Army Tank and Automotive Command (TACOM) and Cummins Engine Co. in the early 1980s [60], led to the development of a prototype engine that

was placed in a military truck. The high temperature and thermal insulating properties of zirconia coatings were examined in an attempt to retain the maximum amount of heat content in the exhaust gas and reduce or eliminate engine cooling. (Approximately 50% of engine field failures, both commercial and military, were related to the cooling system.) This uncooled, low-heat rejection engine had the entire combustion area insulated with a thin zirconia coating. The engine was redesigned to have 361 fewer parts than the standard diesel engine. The omitted parts were mainly from the cooling system and included the radiator, fan, and water pump. Removal of these parts resulted in a 0.56 m^3 (20 ft^3) decrease in engine volume and a reduction in the net weight of the engine by 153 kg (338 lb). Road testing of over 129,000 km (80,000 mi) showed an improvement in fuel economy of 50%, from 6 mpg to 9 mpg.

Since this early work, the use of TBCs has grown; the state-of-the-art coating material is ZrO_2 , with a content between 6 and 12 weight-percent Y_2O_3 . Adding this amount of Y_2O_3 yields a fully-stabilized ZrO_2 material that provided the necessary thermal insulation. Although these coatings showed great promise, there were barriers to their widespread use. One barrier was that the coating adhered poorly to the metal substrate, which limits the coating lifetime and durability. In an engine environment, a coating experiences severe thermal cycling. This thermal cycling resulted in the initiation and growth of thermal-shock-induced cracking at the coating/substrate interface, which ultimately leads to spallation of the coating and exposure of the underlying metal. This led to the development of a duplex coating system, where an MCrAlY (typically $M = \text{Ni}$) bond coat ($\approx 0.1 \text{ mm}$ thick) is deposited on the metal prior to depositing the TBC. This bond coat improves the adherence of the TBC and serves as an oxidation barrier for the metal. Other systems of multilayered coatings or functionally graded materials (FGMs) have also been examined with success [61–63].

5.3 Environmental Barrier Coatings. A long-range goal of the military is to develop engines that can handle alternate fuels (i.e., various grades of gasoline, diesel, and shale oil or coal-derived fuels) without requiring physical adjustment to the engine or compromising engine performance [64]. Low-grade fuels commonly contain parts per million of one or more of the


following: Na, S, K, and V. During the combustion process, reactions can occur involving these impurities, creating compounds that can corrode engine components.

Typically, corrosion is only a problem between the melting point and the dew point of the corrosive media, since in this temperature range the corrosive compounds are fluid and can rapidly spread, enhancing the corrosion process. Below the melting point, transport is too slow; thus, the corrosion rate is very limited. Above the dew point, thermodynamics inhibit the formation of the corrosive media due to evaporation. However, higher pressures increase the dew point and thus the temperature range in which corrosion is possible. Since advanced engines are expected to operate at higher temperatures and pressures it is important to understand how the various corrosive media affect T/EBC materials.

5.3.1 Interaction of ZrO_2 and Typical Corrosive Media. How does ZrO_2 and its stabilizing oxides react with typical corrosive media produced in an engine combustion process? This question must be answered to understand how to develop ZrO_2 -based T/EBCs for engine applications. Zirconia stabilized with Y_2O_3 or CeO_2 are the materials typically used for engine applications. Some of the most common corrosive media are molten salts containing sulfur and/or vanadium.


5.3.2 Interaction of Zirconia and Its Stabilizing Oxides With Sulfur Compounds. Molten salts containing Na are formed during engine combustion; they “leach” the cation (Y^{+3} or Ce^{+4}) from the ZrO_2 , causing surface destabilization and property degradation. This leaching phenomenon is analogous to the hypotheses proposed by Lange et al. [32] to account for the catastrophic degradation of Y-TZP materials that can occur at low temperatures in the presence of water vapor.

Barkalow and Petit [65] first proposed that yttrium is leached from a Y_2O_3 -stabilized zirconia by the following sulfation reaction:



This reaction depends on the partial pressure of SO_3 . A partial pressure increase in SO_3 at elevated temperatures speeds the removal of yttrium. Later work confirmed the high reactivity of Y_2O_3 with SO_3 and yielded a similar reaction, but this work suggested $\text{Y}_2\text{O}_2(\text{SO}_4)_3$ or $\text{Y}_2(\text{SO}_4)_3$ as sulfation products [66]. These tests showed that Y_2O_3 was so reactive, the equilibrium partial pressure of SO_3 could not be measured at 700 °C.

Jones et al. [67] examined the sulfation of pure CeO_2 and pure ZrO_2 . They concluded that the sulfation of CeO_2 followed the equation



at temperatures above 650 °C and combined with an SO_3 pressure of 30 Pa and higher. The ZrO_2 is difficult to sulfate. It remains essentially unsulfated at SO_x partial pressures of ≈ 1000 Pa at 700 °C. Therefore, the hot corrosion resistance of ZrO_2 materials by Na_2SO_4 depends on the stabilizer rather than the zirconia. The thermodynamic data indicate that CeO_2 - ZrO_2 will be more resistant to corrosion by molten Na_2SO_4 than the Y_2O_3 - ZrO_2 . As previously mentioned, plasma-sprayed CeO_2 - ZrO_2 has been patented as a corrosion-resistant coating for superalloys [36].

5.3.3 Interaction of ZrO_2 and Its Stabilizing Oxides With Vanadium Compounds. Jones et al. [68] showed that the reaction between the vanadium-based corrosive media and ceramic oxides, such as Y_2O_3 , CeO_2 , and ZrO_2 , follows a Lewis acid-base mechanism. These oxide additives were reacted with Na_3VO_4 , NaVO_3 , and V_2O_5 . Table 1 summarizes these findings. None of the ceramic oxides reacted with Na_3VO_4 . While CeO_2 and ZrO_2 did not react with NaVO_3 , Y_2O_3 did react to form YVO_4 . YVO_4 was also the product when Y_2O_3 reacted with V_2O_5 , and CeVO_4 when CeO_2 reacted with V_2O_5 . ZrO_2 also exhibited some reactivity producing

Table 1. Reaction Behavior and Products for Ceramic Oxide-Vanadium Compounds [68].

Increasing Acidity
→

		Na_3VO_4	NaVO_3	V_2O_5
Increasing Acidity ↓	Y_2O_3	NR ^a	YVO_4	YVO_4
	CeO_2	NR	NR	CeVO_4
	ZrO_2	NR	NR	ZrV_2O_7 (slowly)

^aNR = No Reaction.

ZrV_2O_7 , but this reaction was extremely slow. Again, these findings show that the stabilizing cation can be leached from ZrO_2 , and that the stabilizing oxide in ZrO_2 will limit the materials' corrosion resistance. More importantly, however, the tendency to react is based on an acid-base relationship between the oxide and molten salt. The more acidic the ceramic oxide, the more corrosion resistant the material. Hence, research has begun to investigate oxides which were more acidic than either Y_2O_3 or CeO_2 .

5.3.4 Scandium and Indium Oxides as Hot-Corrosion-Resistant Stabilizers for ZrO_2 . A review of other rare-earth oxides shows that 5 weight-percent of Sc_2O_3 is effective in stabilizing t- ZrO_2 [69]. It also happens to be significantly more acidic than Y_2O_3 . Studies have shown that Sc_2O_3 essentially did not react with NaVO_3 [37] or V_2O_5 [39], even after hundreds of hours at elevated temperatures. In the latter, the reaction could be enhanced by increasing the partial pressure of SO_3 , which in turn increased the concentration of V_2O_5 . Even with an enhanced reaction, the scandia-stabilized ZrO_2 was still superior to its Y_2O_3 counterpart.

Indium oxide is another oxide that Jones examined for improving the corrosion resistance of TBCs [39]. Pure In_2O_3 was more resistant to reactions with sulfur and vanadium molten salts than either Y_2O_3 or Sc_2O_3 . A sol-gel processed ZrO_2 containing 3.9 mole-percent of In_2O_3

(which was sufficient to produce a material that was 100% tetragonal) was more resistant to corrosion by molten vanadium compounds than commercially available Y_2O_3 - ZrO_2 T/EBCs.

6. Summary

The addition of select oxides to stabilize the tetragonal form of zirconia at room temperature has resulted in a variety of interesting zirconia-based materials with excellent room temperature strength and toughness. The high strength and toughness is due to the transformation of the metastable t-grains. These materials are widely used in cutting tool and wear applications, and are finding increasing applications in the biomedical field. However, the selection of the stabilizing oxide and its role in controlling the $t \rightarrow m$ transformation has also limited the usefulness of these materials.

The enhanced room temperature strength and toughness of PSZ and TZP materials unfortunately diminishes upon exposure to elevated temperatures for long times or extensive thermal cycling. Advances have not been made to maintain the room temperature properties to PSZs and TZPs viable for high-temperature structural applications such as engine components. On the other hand, thermal and environmental barrier coatings are providing excellent thermal and/or corrosion protection to metal components in some engine applications. Further improvements in the corrosion resistance of these coatings is still needed, but research currently underway indicates that coatings with improved resistance may be available soon.

INTENTIONALLY LEFT BLANK.

7. References

1. Heuer, A. H., and L. W. Hobbs (editors). *Advances in Ceramics, Volume 3, Science and Technology of Zirconia*. The American Ceramic Society, Westerville, OH, 1981.
2. Clauseen, N., M. Rühle, and A. H. Heuer (editors). *Advances in Ceramics, Volume 12, Science and Technology of Zirconia*. The American Ceramic Society, Westerville, OH, 1984.
3. Somiya, S., N. Yamamoto, and H. Hanagida (editors). *Advances in Ceramics, Volumes 24A and 24B, Science and Technology of Zirconia*. The American Ceramic Society, Westerville, OH, 1988.
4. Garvie, R. C., R. H. Hannick, and R. T. Pascoe. "Ceramics Steel?" *Nature*, vol. 258, pp. 703–704, 1975.
5. Viechnicki, D. J., and V. S. Stubican. "Mechanisms of Decomposition of the Cubic Solid Solutions in the System ZrO_2 -MgO." *Journal of the American Ceramic Society*, vol. 48, no. 6, pp. 292–297, 1965.
6. Grain, C. F. "Phase Relations in the ZrO_2 -MgO System." *Journal of the American Ceramic Society*, vol. 50, no. 6, pp. 288–290, 1967.
7. Duwez, P., F. Odell, and F. H. Brown. "Stabilization of Zirconia with Calcia and Magnesia." *Journal of the American Ceramic Society*, vol. 35, no. 5, pp. 107–113, 1952.
8. Garvie, R. C. "The Cubic Field in the System CaO- ZrO_2 ." *Journal of the American Ceramic Society*, vol. 51, no. 10, 553–556, 1968.
9. Hellman, J. R., and V. S. Stubican. "Stable and Metastable Phase Relations in the System ZrO_2 -CaO." *Journal of the American Ceramic Society*, vol. 66, no. 4, pp. 260–264, 1983.
10. Scott, H. G. "Phase Relations in the Zirconia-Yttria System." *Journal of Materials Science*, vol. 10, pp. 1527–1535, 1975.
11. Stubican, V. S., R. C. Hink, and S. P. Ray. "Phase Equilibria and Ordering in the System ZrO_2 - Y_2O_3 ." *Journal of the American Ceramic Society*, vol. 61, nos. 1-2, pp. 18–21, 1978.
12. Lanteri, V., A. H. Heuer, and T. E. Mitchell. "Tetragonal Phase in the System ZrO_2 - Y_2O_3 ." *Advances in Ceramics, Volume 12, Science and Technology of Zirconia*, edited by N. Clauseen, M. Rühle, and A. H. Heuer, The American Ceramic Society, Westerville, OH, pp. 1118–1130, 1984.

13. Lange, F. F. "Transformation Toughening, Part 5 – Effect of Temperature and Alloy on Fracture Toughness." *Journal of Materials Science*, vol. 17, pp. 255–262, 1982.
14. Tsukuma, K., and M. Shimada. "Strength, Fracture Toughness and Vickers Hardness of Ce O₂-Stabilized Tetragonal ZrO₂ Polycrystals (Ce-TZP)." *Journal of Materials Science*, vol. 20, pp. 1178–1184, 1985.
15. Duh, J. G., W. Y. Hsu, and B. S. Chiou. "Study of Rare-Earth-Oxide-Doped Yttria Tetragonal Zirconia." *High Tech Ceramics*, pp. 1281–1288, edited by P. Vicenzini, Elsevier Science Publishers B.V., Amsterdam, The Netherlands, 1987.
16. Duran, P., F. Capel, J. R. Jurado, C. Pascual, and C. Moure. "Preparation, Microstructure and Mechanical Properties of Y₂O₃(Er₂O₃) Doped Tetragonal Zirconia." *High Tech Ceramics*, pp. 1289–1295, edited by P. Vicenzini, Elsevier Science Publishers B.V., Amsterdam, The Netherlands, 1987.
17. Pyda, W., K. Haberko, and Z. Zurek. "Zirconia Stabilized With a Mixture of the Rare Earth Oxides." *Journal of the European Ceramic Society*, vol. 10, pp. 453–459, 1992.
18. Log, T., R. A. Cutler, J. F. Jue, and A. V. Virkar. "Polycrystalline t'-ZrO₂(Ln₂O₃) Formed by Displacive Transformations." *Journal of Materials Science*, vol. 28, pp. 4503–4509, 1993.
19. Naskar, M. K., and D. Ganguli. "Rare-Earth Doped Zirconia Fibres by Sol-Gel Processing." *Journal of Materials Science*, vol. 31, pp. 6263–6267, 1996.
20. Duran, P. "The System Erbium-Zirconia." *Journal of the American Ceramic Society*, vol. 60, nos. 11–12, pp. 510–513, 1977.
21. Larsen, D. C., and J. W. Adams. "Long-Term Stability and Properties of Zirconia Ceramics for Heavy Duty Diesel Engine Components." DOE/NASA/0395-1, prepared for the National Aeronautics and Space Administration, Lewis Research Center, Cleveland, OH, for U.S. Department of Energy, Conservation and Renewable Energy, Office of Vehicle and Engine R&D, Washington, DC, September 1985.
22. Stubican, V. S., and S. P. Ray. "Phase Equilibria and Ordering in the System ZrO₂-CaO." *Journal of the American Ceramic Society*, vol. 60, no. 11, pp. 534–537, 1977.
23. Hannink, R. H. J., K. A. Johnston, R. T. Pascoe, and R. C. Garvie. "Microstructural Changes During Isothermal Aging of a Calcia Partially Stabilized Zirconia Alloy." *Advances in Ceramics, Volume 3, Science and Technology of Zirconia*, pp. 116–136, edited by A. H. Heuer and L.W. Hobbs, The American Ceramic Society, Westerville, OH, 1981.

24. Masaki, T. "Mechanical Properties of Y_2O_3 -Stabilized Tetragonal ZrO_2 Polycrystals After Ageing at High Temperatures." *Journal of the American Ceramic Society*, vol. 69, no. 7, pp. 519–522, 1986.
25. Swab, J. J. "Properties of Yttria-Tetragonal Zirconia Polycrystal (Y-TZP) Materials After Long-Term Exposure to Elevated Temperatures." MTL TR 89-21, U.S. Army Research Laboratory, Aberdeen Proving Ground, MD, March 1989.
26. Kobayashi, K., H. Kuwajima, and T. Masaki. "Phase Change and Mechanical Properties of ZrO_2 - Y_2O_3 Solid Electrolyte After Aging." *Solid State Ionics*, vol. 3, pp. 489–493, 1981.
27. Sato, T., S. Ohtaki, and M. Shimada. "Transformation of Yttria Partially Stabilized Zirconia by Low Temperature Annealing in Air." *Journal of Materials Science*, vol. 20, pp. 1466–1470, 1985.
28. Sato, T., S. Ohtaki, T. Endo, and M. Shimada. "Changes in Crystalline Phase and Microstructure on the Surface of Yttria-Doped Tetragonal Zirconia Polycrystals (Y-TZP) by Annealing in Humid Conditions." *Advances in Ceramics, Volume 24A, Science and Technology of Zirconia*, pp. 501–508, edited by S. Somiya, N. Yamamoto, and H. Hanagida, The American Ceramic Society, Westerville, OH, 1988.
29. Swab, J. J. "Low Temperature Degradation of Y-TZP Materials." *Journal of Materials Science*, vol. 26, p. 6706, 1991.
30. Yoshimura, M., T. Noma, K. Kawabata, and S. Somiya. "Role of H_2O on the Degradation Process of Y-TZP." *Journal of Materials Science Letters*, vol. 6, pp. 465–467, 1987.
31. Yoshimura, M., T. Noma, K. Kawabata, and S. Somiya. "The Effects of High Temperature and High Pressure Water on the Low Temperature Degradation Behavior of Y-TZP." *Journal of the Ceramic Society of Japan, International Edition*, vol. 96, pp. 263–268, 1988.
32. Lange, F. F., G. L. Dunlop, and B. I. Davis. "Degradation During Aging of Transformation-Toughened ZrO_2 - Y_2O_3 Materials at 250 C." *Journal of the American Ceramic Society*, vol. 69, no. 3, pp. 237–240, 1986.
33. Winnubst, A. J. A., and A. J. Burggaraaf. "The Aging Behavior of Ultrafine-Grained Y-TZP in Hot Water." *Advances in Ceramics, Science and Technology of Zirconia*, pp. 39–47, edited by S. Somiya, N. Yamamoto, and H. Hanagida, The American Ceramic Society, Westerville, OH, vol. 24, 1988.
34. Lange, F. F. "Transformation Toughening – Part 3 Experimental Observations in the ZrO_2 - Y_2O_3 System." *Journal of Materials Science*, vol. 17, pp. 240–246, 1982.

35. Duwez, P., and P. J. Odell. "Phase Relationships in the System Zirconia-Ceria." *Journal of the American Ceramic Society*, vol. 33, no. 9, pp. 274–283, 1950.
36. Siemers, P. A., and D. W. McKee. "Method of Coating a Superalloy Substrate, Coating Compositions, and Composites Obtained Therefrom." U.S. Patent 4,328,285, 1982.
37. Jones, R. L. "Scandia as a Corrosion-Resistant Stabilizer for Zirconia." NRL Memorandum Report 6332, Naval Research Laboratory, Washington, DC, September 1988.
38. Jones, R. L. "Hot Corrosion Resistance of Scandia Stabilized Zirconia Coatings." *Corrosion and Corrosive Degradation of Ceramics, Ceramic Transaction*, vol. 10, pp. 291–308, edited by R. E. Tressler and M. McNallan, The American Ceramic Society, Westerville, OH, 1990.
39. Jones, R. L., and D. Mess. "India as a Hot Corrosion-Resistant Stabilizer for Zirconia." *Journal of American Ceramic Society*, vol. 75, no. 7, pp. 1818–1821, 1992.
40. Rühle, M., and A. H. Heuer. "Phase Transformations in ZrO₂-Containing Ceramics: II, The Martensitic Reaction in t-ZrO₂." *Advances in Ceramics, Volume 12, Science and Technology of Zirconia*, pp. 14–32, edited by N. Clauseen, M. Rühle, and A.H. Heuer, The American Ceramic Society, Westerville, OH, 1984.
41. Swab, J. J., and S. C. Stowell. "Properties of a TZP/Al₂O₃ Composite After Long-Term Exposure to 1000 °C." U.S. Army Materials Technology Laboratory, MTL TR 91-54, NTIS Access No. ADA-246407, December 1991.
42. Tsukuma, K., K. Ueda, and M. Shimada. "Strength and Fracture Toughness of Isostatically Hot-Pressed Composites of Al₂O₃ and Y₂O₃-Partially-Stabilized ZrO₂." *Journal of the American Ceramic Society*, vol. 68, no. 1, pp. C4–C5, 1985.
43. Claussen, N., and M. Rühle. "Design of Transformation Toughened Ceramics." *Advances in Ceramics, Volume 3, Science and Technology of Zirconia*, pp. 137–163, edited by A. H. Heuer and L. W. Hobbs, The American Ceramic Society, Westerville, OH, 1981.
44. Claussen, N. "Strengthening Strategies for ZrO₂-Toughened Ceramics at High Temperature." *Materials Science and Engineering*, vol. 71, pp. 23–33, 1985.
45. Wallace, J. S., G. Petzow, and N. Claussen. "Microstructure and Property Development in In-Situ Reacted Mullite-ZrO₂ Composites." *Advances in Ceramics, Volume 12, Science and Technology of Zirconia*, pp. 436–442, edited by N. Clauseen, M. Rühle, and A. H. Heuer, The American Ceramic Society, Westerville, OH, 1984.
46. Falk, L. K. L., T. Hermansson, and K. Rundgren, "Microstructure of Hot-Pressed Si₃N₄-ZrO₂(+Y₂O₃) Composites." *Journal of Materials Science Letters*, vol. 8, pp. 1032–1034, 1989.

47. Claussen, N., and C. P. Lahmann. "Fracture Behavior of Some Hot-Pressed Si_3N_4 Ceramics at High Temperatures." *Powder Metallurgy International*, vol. 7, no. 3, pp. 133–135, 1975.
48. Claussen, N., K. L. Weisskopf, and M. Rühle. "Tetragonal Zirconia Polycrystals Reinforced With SiC Whiskers." *Journal of the American Ceramic Society*, vol. 69, no. 3, pp. 288–292, 1986.
49. Wantanabe, T., and K. Shobu. "Mechanical Properties of Hot-Pressed $\text{TiB}_2\text{-ZrO}_2$ Composites." *Journal of the American Ceramic Society*, vol. 68, pp. C34–C36, 1985.
50. Heuer, A. H., and M. Rühle. "Overview No. 45: On the Nucleation of the Martensitic Transformation in Zirconia (ZrO_2)." *Acta Metallurgica*, vol. 33, no. 12, pp. 2101–2112, 1985.
51. Lange, F. F. "Transformation Toughening, Part 1 – Size Effects Associated With the Thermodynamics of Constrained Transformations." *Journal of Materials Science*, vol. 17, pp. 225–234, 1982.
52. Evans, A. G. "Toughening Mechanisms in Zirconia Alloys." *Advances in Ceramics, Volume 12, Science and Technology of Zirconia*, pp. 193–212, edited by N. Clauseen, M. Rühle, and A. H. Heuer, The American Ceramic Society, Westerville, OH, 1984.
53. Green, D. J., R. H. J. Hannink, and M. V. Swain. *Transformation Toughening of Ceramics*. CRC Press, 1989.
54. Smith, R. W., and R. D. Fast. "The Future of Thermal Spray Technology." *Welding Journal*, pp. 43–50, July 1994.
55. Howes, C. P. Jr., "An Overview of Thermal Spray Processes." *Materials Technology*, vol. 11, pp. 188–194, 1996.
56. Van den Berge, F. M. J. "Thermal Spray Processes—An Overview." *Advanced Materials and Process*, pp. 31–34, December 1998.
57. Sampth, S., H. Herman, N. Shimoda, and T. Saito. "Thermal Spray Processing of FGMs." *MRS Bulletin*, pp. 27–31, January 1995.
58. Kvernes, I., and P. Fartum. "Use of Corrosion-Resistant Plasma Sprayed Coatings in Diesel Engines." *Thin Solid Films*, vol. 53, pp. 259–269, 1978.
59. Kamo, R., and W. Bryzik. "Adiabatic Turbocompound Engine Performance Prediction." SAE Paper 730-068, Society of Automotive Engineers, Inc., Warrendale, PA, 1978.

60. Katz, R. N. "Applications of High Performance Ceramics in Heat Engine Design." *Engineering Ceramics*, pp. 227-249, edited by M. Ish-Shalom and D. G. Brandon, New York: Elsevier Applied Science Publishers, 1984.
61. Yonushonis, T. M. "Overview of Thermal Barrier Coatings in Diesel Engines." *Journal of Thermal Spray Technology*, vol. 6, no.1, pp. 50-56, March 1997.
62. Steffens, H. D., and R. Kaczmarek. "Thermal Barrier Coatings for Heat Engines." *Welding in the World*, vol. 28, no.11, pp. 224-230, 1990.
63. Scott, K. T. "Plasma Sprayed Thermal Barrier Coatings for Diesel Engines." *Applications of Materials Technology in Engines*, Mechanical Engineering Publications Limited, UK, pp. 41-49, 1992.
64. Glance, P. C., and R. Munt. "Engine Research, Development, and Acquisition Strategy for the U.S. Army Group Vehicles." SAE Paper 830674, Society of Automotive Engineers International Congress and Exposition, Detroit, MI, pp. 1-13, 1983.
65. Barkalow, R., and F. Pettit. "Mechanisms of Hot Corrosion Attack of Ceramic Coating Materials." *Proceedings of the 1st Conference on Advanced Materials for Alternative Fuel Capable Directly Fired Heat Engines*, CONF-700749, pp. 704-710, edited by J. W. Fairbanks and J. Stinger, National Technical Information Service, Springfield, VA, 1979.
66. Jones, R. L., D. B. Nordman, and S. T. Gadomski. "Sulfation of Y_2O_3 and HfO_2 in Relation to MCrAl Coatings." *Metallurgical Transactions*, vol. 16a, no. 2, pp. 303-306, 1985.
67. Jones, R. L., S. R. Jones, and C. E. Williams. "Sulfation of CeO_2 and ZrO_2 Relating to Hot Corrosion." *Journal of the Electrochemical Society*, vol. 132, no. 6, pp. 1498-1501, 1985.
68. Jones, R. L., C. E. Williams, and S. R. Jones. "Reaction of Vanadium Compounds with Ceramic Oxides." *Journal of the Electrochemical Society*, vol. 133, no.1, pp. 227-230, 1986.
69. Ruh, R., H. J. Garrett, R. F. Domagala, and V. A. Patel. "System Zirconia-Scandia." *Journal of the American Ceramic Society*, vol. 60, nos. 9-10, pp. 399-403, 1977.

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFORMATION CENTER DTIC OCA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218	3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI LL 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	HQDA DAMO FDT 400 ARMY PENTAGON WASHINGTON DC 20310-0460	3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI IS T 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	OSD OUSD(A&T)/ODDR&E(R) DR R J TREW 3800 DEFENSE PENTAGON WASHINGTON DC 20301-3800		<u>ABERDEEN PROVING GROUND</u>
1	COMMANDING GENERAL US ARMY MATERIEL CMD AMCRDA TF 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001	2	DIR USARL AMSRL CI LP (BLDG 305)
1	INST FOR ADVNCD TCHNLGY THE UNIV OF TEXAS AT AUSTIN 3925 W BRAKER LN STE 400 AUSTIN TX 78759-5316		
1	US MILITARY ACADEMY MATH SCI CTR EXCELLENCE MADN MATH THAYER HALL WEST POINT NY 10996-1786		
1	DIRECTOR US ARMY RESEARCH LAB AMSRL D DR D SMITH 2800 POWDER MILL RD ADELPHI MD 20783-1197		
1	DIRECTOR US ARMY RESEARCH LAB AMSRL CI AI R 2800 POWDER MILL RD ADELPHI MD 20783-1197		

NO. OF
COPIES

ORGANIZATION

2 CTR FOR THERMAL SPRAY RSH
DEPT OF MTRL SCIENCE & ENGR
STATE UNIV OF NEW YORK
H HERMAN
S SAMPATH
STONY BROOK NY 11794-2275

ABERDEEN PROVING GROUND

13 DIR USARL
AMSRL WM BC
J SWAB (10 CPS)
P HUANG
J ADAMS
A WEREZCZAK

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project(0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE September 2001	3. REPORT TYPE AND DATES COVERED Final, January-May 1999		
4. TITLE AND SUBTITLE Role of Oxide Additives in Stabilizing Zirconia for Coating Applications			5. FUNDING NUMBERS 08M43D	
6. AUTHOR(S) Jeffrey J. Swab				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRL-WM-MC Aberdeen Proving Ground, MD 21005-5069			8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TR-2591	
9. SPONSORING/MONITORING AGENCY NAMES(S) AND ADDRESS(ES)			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) <p>Zirconium dioxide (ZrO₂) is a ceramic with a variety of industrial applications as a refractory material, and it is used in electronic packaging, biomedicine, and advanced engines. Unfortunately, pure zirconia undergoes a destructive phase transformation that severely limits its uses. However, some oxide additives have been found to control this transformation and ultimately lead to significant improvements in the material. This report summarizes the role that oxide additives play in controlling these transformations, and the resulting applications of ZrO₂-based coatings are discussed.</p>				
14. SUBJECT TERMS zirconia, coatings, thermal barrier coatings, transformation toughening, corrosion resistance			15. NUMBER OF PAGES 37	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

INTENTIONALLY LEFT BLANK.