



Interceptor Small Arms Protective Insert (SAPI) MANTECH Product Enhancement Test Report II

by Jeffrey A. Mears, Robert F. Monks, Robert Wolffe,
and James F. Mackiewicz

ARL-CR-488

February 2002

prepared by

Jeffrey A. Mears, Robert F. Monks, and Robert Wolffe
Simula Safety Systems Inc.
7822 South 46th Street
Phoenix, AZ 85044

James F. Mackiewicz
U.S. Army Natick Soldier Center
AMSSB-RIP-MC(N)
Natick, MA 01760-5011

under contract

DAAN02-98-D-5007-009

Approved for public release; distribution is unlimited.

Army Research Laboratory

Aberdeen Proving Ground, MD 21005-5069

ARL-CR-488

February 2002



Interceptor Small Arms Protective Insert (SAPI) MANTECH Product Enhancement Test Report II

Jeffrey A. Mears, Robert F. Monks, and Robert Wolffe
Simula Safety Systems Inc.

James F. Mackiewicz
U.S. Army Natick Soldier Center

prepared by

Simula Safety Systems Inc.
7822 South 46th Street
Phoenix, AZ 85044

U.S. Army Natick Soldier Center
AMSSB-RIP-MC(N)
Natick, MA 01760-5011

under contract

DAAN02-98-D-5007-009

Abstract

This report summarizes the work performed by Specialty Plastic Products of Pennsylvania Inc. and their subcontractor, Simula Safety Systems Inc., under the Manufacturing Technology (MANTECH) program sponsored by the U.S. Army Materiel Command and executed by the U.S. Army Natick Soldier Center. The objective of this effort was to investigate M Cubed Technologies Inc.'s siliconized silicon carbide armor material and process as an alternative ceramic component for the multi-Service Interceptor Small Arms Protective Inserts (SAPI).

Contents

List of Figures	v
List of Tables	v
1. Introduction	1
2. SAPI Optimization Effort	1
2.1 Tile-to-Laminate Ratio.....	1
2.2 Alternative Composite Backings	3
2.2.1 KM2/SS Hybrid	3
2.2.2 KM2/SS/KM2 Hybrid	3
2.2.3 KM2 Polyurethane Film Stack Laminate	4
2.2.4 Twaron Polyurethane Film Stack Laminate	4
2.2.5 Twaron Spall Liner (Rubberized Resin).....	5
2.2.6 KM2 Polyethylene Film Stack	5
2.2.7 SSC-A3 Ceramic Material	5
2.2.8 Ultra-High Pressure SS.....	5
2.2.9 Ultra-High-Pressure SS Plus.....	6
2.3 V_0 Verification Testing	6
3. Conclusions	9
Distribution List	9
Report Documentation Page	15

INTENTIONALLY LEFT BLANK.

List of Figures

Figure 1. Threat A tile-to-laminate ratio.....	2
Figure 2. Threat B tile-to-laminate ratio.....	3
Figure 3. Threat A laminate backing study.....	4

List of Tables

Table 1. Tile-to-laminate ratio test series for threats A and B.....	2
Table 2. SSC-A1 threat A V_0 testing.....	7
Table 3. SSC-A1 threat B V_0 testing.....	7
Table 4. SSC-A3 threat A V_0 testing.....	7
Table 5. SSC-A3 threat B V_0 testing.....	9

INTENTIONALLY LEFT BLANK.

1. Introduction

As described in U.S. Army Materiel Command Acquisition Center (USAMCAC) contract no. DAAN02-98-D-5007-009, line item 1004, Manufacturing Technology (MANTECH) statement of work, the contractor “shall investigate proprietary M Cubed ceramic material and material processes that will potentially provide cost-reduction benefits to the U.S. Marine Corps.” Simula Safety Systems Inc.* has identified this material as an alternate to the boron carbide (B_4C) ceramic material, which is used as the strike face on the current Interceptor Small Arms Protective Insert (SAPI) plates. This new ceramic material is a “Reaction Bonded Silicon carbide” material developed by M Cubed Technologies Inc. (M Cubed).† The new ceramic material is significantly lower in cost compared to the present hot-pressed B_4C material. The lower cost of the ceramic tile is a result of inexpensive manufacturing processes employed by M Cubed. This document will summarize the efforts involved in developing the design to meet the current Interceptor SAPI requirements.

2. SAPI Optimization Effort

2.1 Tile-to-Laminate Ratio

In order to optimize the SAPI design using the M Cubed material, we first needed to understand the relationship between tile thickness to laminate thickness as related to overall armor system areal density. Therefore, the first test series was performed to define this relationship. Since the insert areal density is a constant (in order to yield an insert of known weight) of 4.8 psf, the question here was one of tile weight (thickness) to laminate weight (number of plies). This ratio has been explored before on the baseline B_4C /Spectra Shield (SS) system, but only at a minimal effort level. The effort performed here was to fully characterize this relationship for both the threat A and B projectiles. Five tile-to-laminate ratio armor systems were tested for each projectile as outlined in Table 1. These tests were performed on a clay backing using a 28-ply 600 denier Kevlar KM2 outer tactical vest (OTV) simulant between the back face of the target and the clay block.

*Simula Safety Systems Inc., 7822 S. 46th Street, Phoenix, AZ 85044.

†M Cubed Technologies Inc., 921 Main Street, Monroe, CT 06468.

Table 1. Tile-to-laminate ratio test series for threats A and B.

% Tile	% Laminate	Tile Thickness	Plies of Spectra Shield
50	50	0.150	90
60	40	0.180	72
70	30	0.210	54
80	20	0.245	34
90	10	0.275	17

To obtain the most useful information, this testing determined V_{50} velocities for each armor system. The resulting information was plotted on a graph (Figures 1 and 2) to visually determine the optimal tile-to-laminate ratio.

As shown in Table 1, the 60% tile/40% laminate armor system is the optimal choice for further armor system development. Even though the 50/50% system produced a higher V_{50} for the threat A projectile, the threat B testing showed a lower V_{50} for the 50/50% system. To further optimize the armor system, we then evaluated several different composite backing systems based on the 60/40% tile/laminate ratio. The results of this testing are summarized in the following sections.

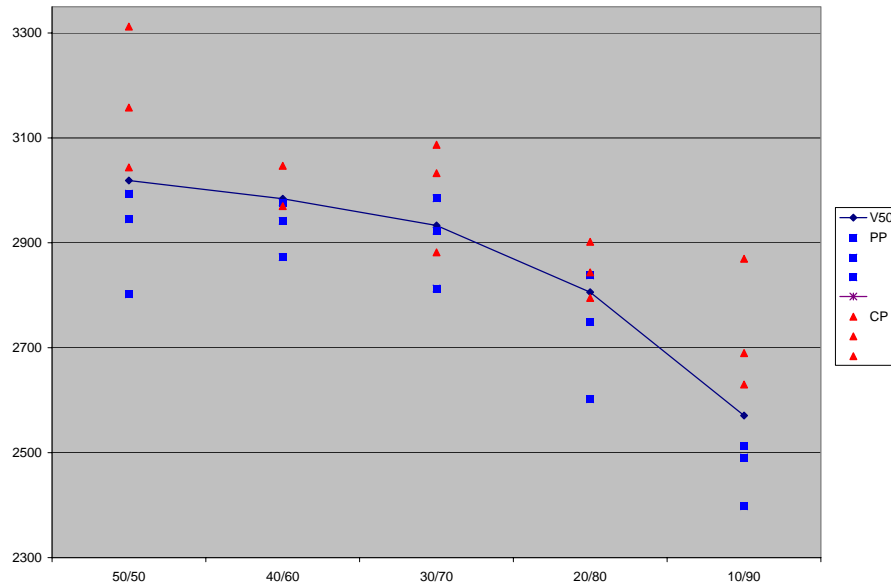


Figure 1. Threat A tile-to-laminate ratio.

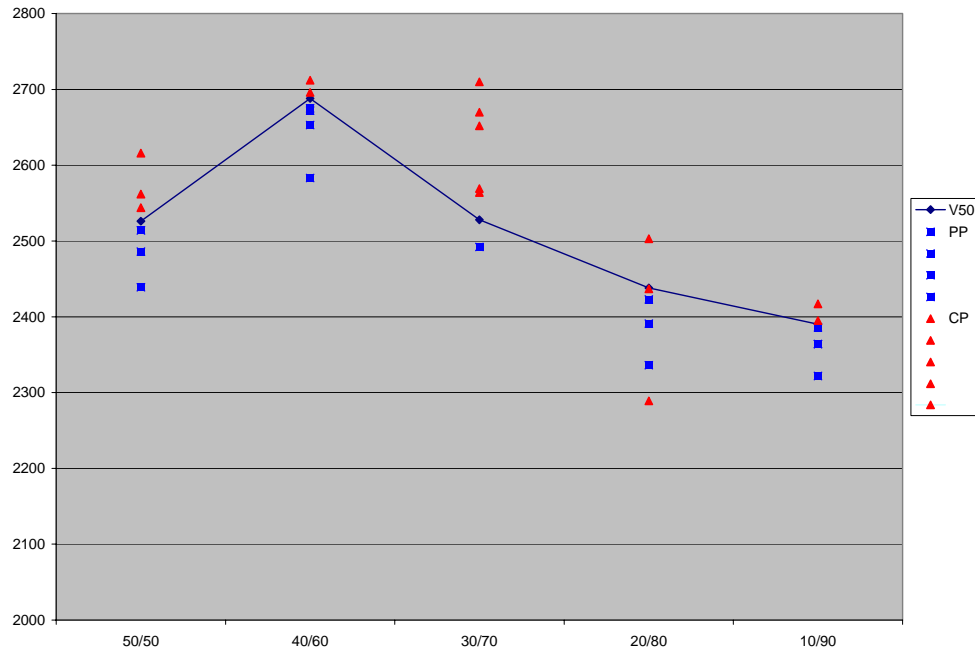


Figure 2. Threat B tile-to-laminate ratio.

2.2 Alternative Composite Backings

2.2.1 KM2/SS Hybrid

In past experiments, it has been shown that support of the ceramic material provides increased ballistic performance. Using KM2 fabric impregnated with vinyl-ester (VE) resin to provide support as well as ballistic resistance, we investigated a KM2 VE/SS hybrid. This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.2.2 KM2/SS/KM2 Hybrid

The use of the KM2 (film stacked with polyurethane) behind the SS was thought to provide a stiffer alternative to the all SS back face. Using KM2 fabric impregnated with VE resin to provide support as well as ballistic

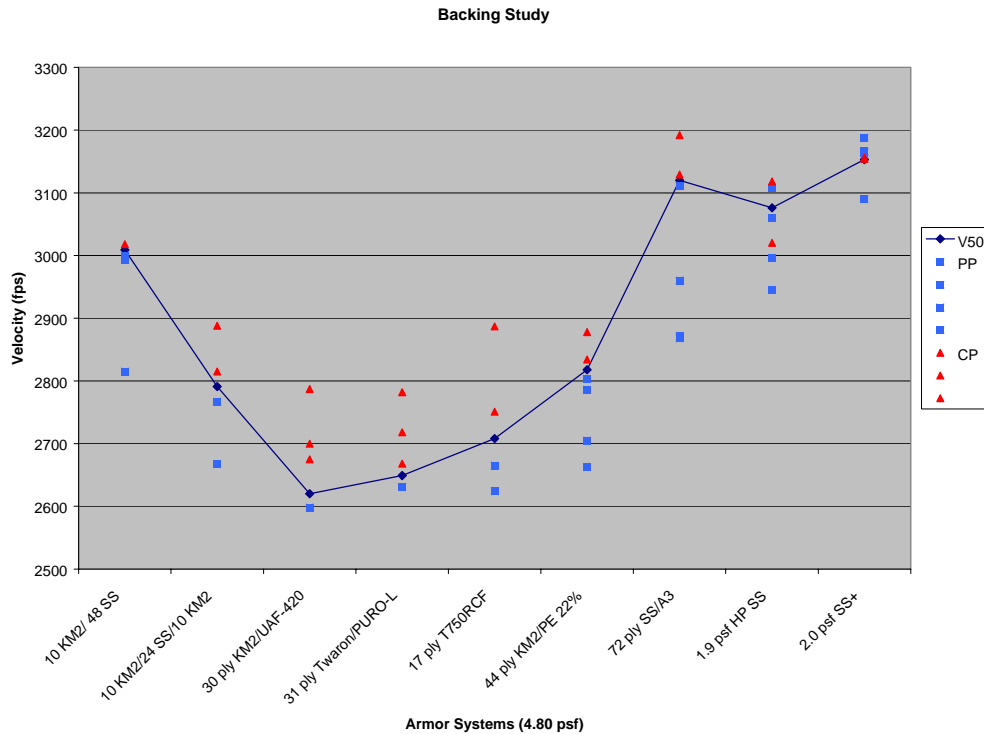


Figure 3. Threat A laminate backing study.

resistance, SS to provide a tough middle layer, and KM2 polyurethane as a stiff ballistic back face, we tested a KM2 VE/SS/KM2 polyurethane film stack hybrid. This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.2.3 KM2 Polyurethane Film Stack Laminate

The use of the KM2 (film stacked with polyurethane) will provide a stiff, supportive yet ballistically viable, composite backing. We tested a KM2 polyurethane film stack laminate. This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.2.4 Twaron Polyurethane Film Stack Laminate

The use of the Twaron (film stacked with PURO-L polyurethane) will provide a stiff, supportive, yet ballistically viable, composite backing. The Twaron material is lower in cost compared to the KM2 style 705 material. We tested a

Twaronpolyurethane film stack laminate. This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.2.5 Twaron Spall Liner (Rubberized Resin)

The use of the Twaron spall liner (with rubberized resin) will provide a stiff, supportive, yet ballistically viable, composite backing. We tested a Twaron spall liner laminate. This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.2.6 KM2 Polyethylene Film Stack

The use of the KM2 (film stacked with polyethylene) will provide a stiff, supportive, yet ballistically viable, composite backing. We tested a KM2 polyethylene film stack laminate. This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.2.7 SSC-A3 Ceramic Material

M Cubed produces several different versions of the reaction bonded silicon carbide material. To this point, we had been using the SSC-A1 material, which has a nominal silicon carbide content of 77%. The SSC-A3 material has a nominal silicon carbide content of 82%, and as such could result in improved ballistic performance. We tested an SSC-A3/SS armor system. This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.2.8 Ultra-High Pressure SS

In past experiments, it has been shown that the use of ultra-high-pressure processed SS material (2500 psi) provides increased ballistic performance. Using preconsolidated laminate supplied by an outside vendor, we investigated an ultra-high-pressure SS armor system. This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the

back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.2.9 Ultra-High-Pressure SS Plus

We wanted to investigate the ultra-high-pressure processing of the SS Plus material being offered by Allied Signal. The laminates were processed by the same outside vendor who supplied the ultra-high-pressure SS laminates discussed in the previous section. The only point of discussion with the SS Plus laminates is that the laminates supplied were 2.0 psf as opposed to 1.9 psf (which were requested). This testing was performed on a clay backing using a 28-ply 600 denier KM2 OTV simulant between the back face of the target and the clay block. The test sample was six targets used to obtain a V_{50} with the threat A projectile. The data was then plotted against the other armor system backing options and is shown in Figure 3.

2.3 V_0 Verification Testing

After the laminate backing study was complete, we determined that the best candidate armor systems were SS based. While the ultra-high-pressure test specimens showed the highest V_{50} results, we determined that the added cost associated with producing these laminates to the SAPI configuration would be too high to support the Interceptor program. Therefore, we concentrated on the lower pressure (150-psi) SS PCR-based* armor systems using the SSC-A1 and SSC-A3 ceramic strike faces. We fabricated 12 SAPI plates, 6 of which were made with 0.173-in SSC-A1 material and 78 plies of SS PCR; the other six were made with 0.173-in SSC-A3 and 76 plies of SS PCR. Both armor systems had areal densities of 4.85 psf. The differences in the ply counts for the two armor systems can be attributed to the different densities of the two ceramic materials (i.e., the SSC-A1 is lighter than the SSC-A3). All 12 test samples were processed at lower pressure (150 psi) in reusable silicon rubber autoclave bags. All 12 test samples had the production durability covers and nylon spall shield attached prior to testing. The verification test results for the SSC-A1 material are summarized in Tables 2 and 3. The verification test results for the SSC-A3 material are summarized in Tables 4 and 5.

*Spectra Shield PCR is a Honeywell Company registered trade name for ballistic laminates.

Table 1. SSC-A1 threat A V₀ testing.

Serial No.	Velocity (fps)	Obliquity (°)	Result	BFD	Comment
032000VF-1	2696	0	PP	1.25	Durability
032000VF-1	2670	0	PP	1.25	Durability
032000VF-1	2797	60	PP	1.12	Durability
3020VF#3	2767	0	PP	1.38	Durability
3020VF#3	2760	0	PP	1.38	Durability
3020VF#3	2738	60	PP	1.12	Durability
032000VF-6	2797	0	PP	1.38	
032000VF-6	2800	0	PP	1.25	
032000VF-6	2787	60	PP	1.00	
032000VF-5	2773	0	PP	1.38	
032000VF-5	2785	0	PP	1.25	
032000VF-5	2786	30	PP	1.38	

Notes: BFD = back face deformation.

PP = partial penetration.

CP = complete penetration.

Table 2. SSC-A1 threat B V₀ testing.

Sample	Velocity (fps)	Obliquity (°)	Result	BFD	Comment
030800VF-2	2339	0	PP	1.12	
030800VF-2	2344	0	PP	1.12	CP on insert
030800VF-2	2351	30	PP	1.12	
3020VF#4	2328	0	PP	1.12	
3020VF#4	2327	0	PP	1.12	
3020VF#4	2319	30	PP	1.12	

Table 3. SSC-A3 threat A V₀ testing.

Serial No.	Velocity (fps)	Obliquity (°)	Result	BFD	Comment
33000VF-1	2754	0	PP	1.37	Durability
33000VF-1	2797	0	PP	1.37	Durability
33000VF-1	2795	30	PP	1.37	Durability
33000VF-2	2788	0	PP	1.37	Durability
33000VF-2	2767	0	PP	1.37	Durability
33000VF-2	2786	30	PP	1.37	Durability
412000VF-6	2791	0	PP	1.25	
412000VF-6	2732	0	PP	1.37	
412000VF-6	2795	30	PP	1.37	
412000VF-5	2767	0	PP	1.37	
412000VF-5	2754	0	PP	1.37	
412000VF-5	2789	30	PP	1.50	

Table 4. SSC-A3 threat B V₀ testing.

Sample	Velocity (fps)	Obliquity (°)	Result	BFD	Comment
412000VF-4	2317	0	PP	1.12	
412000VF-4	2318	0	PP	1.00	
412000VF-4	2287	30	PP	1.00	
412000VF-8	2294	0	PP	1.12	CP on insert, 1 ply KM2
412000VF-8	2313	0	PP	1.00	
412000VF-8	2315	30	PP	1.12	

3. Conclusions

We determined that the optimum tile-to-laminate ratio for threats A and B was 60% tile and 40% laminate by weight. This correlates to an armor system of 0.170- to 0.180-in tile with 76 plies of SS PCR. The testing of the different laminate systems proved that the SS PCR-based armor system is the most desirable from a cost and performance standpoint. The ceramic material of choice is the SSC-A3 material, based on performance and manufacturing economies. Our internal verification testing and subsequent First Article Testing (FAT) at the U.S. Army Aberdeen Test Center (ATC) have validated this armor system as meeting the requirements of the Interceptor SAPI performance requirements.

Table 5. SSC-A3 threat B V₀ testing.

Sample	Velocity (fps)	Obliquity (°)	Result	BFD	Comment
412000VF-4	2317	0	PP	1.12	
412000VF-4	2318	0	PP	1.00	
412000VF-4	2287	30	PP	1.00	
412000VF-8	2294	0	PP	1.12	CP on insert, 1 ply KM2
412000VF-8	2313	0	PP	1.00	
412000VF-8	2315	30	PP	1.12	

3. Conclusions

We determined that the optimum tile-to-laminate ratio for threats A and B was 60% tile and 40% laminate by weight. This correlates to an armor system of 0.170- to 0.180-in tile with 76 plies of SS PCR. The testing of the different laminate systems proved that the SS PCR-based armor system is the most desirable from a cost and performance standpoint. The ceramic material of choice is the SSC-A3 material, based on performance and manufacturing economies. Our internal verification testing and subsequent First Article Testing (FAT) at the U.S. Army Aberdeen Test Center (ATC) have validated this armor system as meeting the requirements of the Interceptor SAPI performance requirements.

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	DEFENSE TECHNICAL INFORMATION CENTER DTIC OCA 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218
1	HQDA DAMO FDT 400 ARMY PENTAGON WASHINGTON DC 20310-0460
1	OSD OUSD(A&T)/ODDR&E(R) DR R J TREW 3800 DEFENSE PENTAGON WASHINGTON DC 20301-3800
1	COMMANDING GENERAL US ARMY MATERIEL CMD AMCRDA TF 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001
1	DIRECTOR US ARMY RESEARCH LAB AMSRL D DR D SMITH 2800 POWDER MILL RD ADELPHI MD 20783-1197
1	DIRECTOR US ARMY RESEARCH LAB AMSRL CI AI R 2800 POWDER MILL RD ADELPHI MD 20783-1197
3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI LL 2800 POWDER MILL RD ADELPHI MD 20783-1197

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
3	DIRECTOR US ARMY RESEARCH LAB AMSRL CI IS T 2800 POWDER MILL RD ADELPHI MD 20783-1197
	<u>ABERDEEN PROVING GROUND</u>
2	DIR USARL AMSRL CI LP (BLDG 305)

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	DIR USARL AMSRL SS 2800 POWDER MILL RD ADELPHI MD 20783-1145	1	US ARMY MEDICAL MATERIAL MCMR MMC B 1423 SULTAN DR STE 100 FT DETRICK MD 21702-5001
1	CDR AMXRO RT OFC RSRCH & TECH INTEGRATION PO BOX 12211 RESEARCH TRIANGLE PARK NC 27709-2211	1	CDR NATICK SC USA NATICK SOLDIER CTR TECHNICAL LIBRARY NATICK MA 01760-5019
1	CDR AMXRO RM DR J BAILEY PO BOX 12211 RESEARCH TRIANGLE PARK NC 27709-2211	15	CDR NATICK SOLDIER CTR J MACKIEWICZ KANSAS ST NATICK MA 01760-5010
1	CDR CAMERON STATION DTIC FDAC BLDG 5 5010 DUKE ST ALEXANDRIA VA 22304	1	CDR NATICK SOLDIER CTR P BRANDLER KANSAS ST NATICK MA 01760-5010
1	DPTY CG FOR RDE US ARMY MATERIAL CMD AMCRDA TF 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001	1	CDR NATICK SOLDIER CTR B G MADDOX KANSAS ST NATICK MA 01760-5010
1	CDR USA ARDEC AMSTA ARCCHC M DANESI PICATINNY ARSENAL NJ 07806-5000	1	CDR USA TANK AUTO CMD AMSTA TSL TECHNICAL LIBRARY WARREN MI 48397-5000
1	ARMY NATIONAL GUARD BUREAU NGB ARO O LTC M NICKELL 111 S GEORGE MASON DR ARLINGTON VA 22204-1382	1	DIR DEFENSE INTEL AGCY ODT 5A WASHINGTON DC 20340-6053
		1	NAVAL RESEARCH LAB DR R BADALIANCE CODE 6684 4555 OVERLOOK AVE SW WASHINGTON DC 20375
		1	CDR AIFRTC G SCHLESINGER APPL TECH BR 220 7TH ST NE CHARLOTTESVILLE VA 22901-5396

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	CDR USA QUARTERMASTER SCHOOL QUARTERMASTER SCHOOL LIBRARY FT LEE VA 23801	1	NATIONAL INSTITUTE OF JUSTICE OFFICE OF LAW ENFORCEMENT K HIGGINS (5 CPS) BLDG 225 RM A323 GAITHERSBURG MD 20899
1	CDR USA ARDEC AMSTA AR AET DR W EBHARA PICATINNY ARSENAL NJ 07806	11	COMMANDING GENERAL MARINE CORPS SYSTEMS CMD CODE CMCC B G FAIGLEY B G DONOVAN LTC BELL LTC NELSON D BRYCE CPT CHURCH MAJ PATRICIO (5 CPS) 22033 BARNETT AVE STE 315 QUANTICO VA 22134-5080
1	CDR NAWCAD UNIT 7 BLDG 439 STE F 47110 LILJENCRANTZ RD PATUXENT RIVER MD 20670-1545		
1	DIR OF MILITARY SUPPORT DAMO ODC COMPIO 400 ARMY PENTAGON WASHINGTON DC 20310-0400	1	PROJECT MANAGER AIRCREW INTEGRATED SYS SFAE AV LSE P CROUCH BLDG 5681 RM 151 REDSTONE ARSENAL AL 35898
1	PM SPECIAL PROJECTS MAJ A EARLE 5951 PUTNAM RD FT BELVOIR VA 22060-5424	2	CDR US ARMY TACOM AMSTA TRS J THOMPSON S GOODMAN WARREN MI 48397-5000
3	PM SOLDIER COL JETTE LTC BADELLE (2 CPS) FORT BELVOIR VA 22060		
1	JTCG AS CENTRAL OFFICE NAVAL AIR SYSTEMS CMD AIR 4 1 8 J JOLLEY 1421 JEFFERSON HIGHWAY ARLINGTON VA 22243-5120	2	HQDA SARD TR R MORRISON R ROHDE 2511 JEFFERSON DAVIS HWY STE 9800 ARLINGTON VA 22202-3911
2	CDR US ARMY INFANTRY CENTER COL HOLTON (2 CPS) FORT BENNING GA 31905-5400	1	HQDA OASA RDA SARD SC RM 3C468 WASHINGTON DC 20310-0103
1	US MILITARY POLICE SCHOOL ATZN MP CM J KOZIABA FORT MCCLELLAN AL 36205-5030	1	HQDA SARDA TD DR C CHURCH WASHINGTON DC 20310
		1	CARDEROCK DIVISION HQS DAVID TAYLOR MDL BASIN R PETERSON BETHESDA MD 20084-5000

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>	<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
2	US ARMY MATERIEL CMD AMCDCG T C W KITCHENS AMCRDA TF C GARDINIER 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001	1	CIA OSWR DSD W WALTMAN RM 5P0110 NHB WASHINGTON DC 20505
1	NAVAL SPECIAL WARFARE DEVELOPMENT GROUP CODE N51 B DEPPEN 1636 REGULUS AVE VIRGINIA BEACH VA 23461-2299	2	DIR LLNL R GOGOLEWSKI MS L290 J REAUGH PO BOX 808 LIVERMORE CA 94550
1	US SECRET SERVICE DIV TECHNICAL SECURITY T THOMAS 1800 G ST NW WASHINGTON DC 20223	1	DIR LLNL R LANDINGHAM L32 PO BOX 808 LIVERMORE CA 94550
1	CDR MARINE CORPS LOGISTICS BASES CODE 835 NBC 814 RADFORD BLVD ALBANY GA 31704-112	2	DIR LANL F ADDESSIO M BURKETT LOS ALAMOS NM 87545
3	SIMULA SAFETY SYSTEMS INC S LYONS J MEIRS R MONKS 7822 S 46TH ST PHOENIX AZ 85044	1	DIR SNL D GRADY MS 0821 PO BOX 5800 ALBUQUERQUE NM 87185-0307
2	CDR NGIC IANG GS MT MS306 J CRIDER W GSTATTENBAUER 2055 BOULDERS ROAD CHARLOTTESVILLE VA 22901-8318	2	DIR SNL M FORRESTAL DIV 1551 PO BOX 5800 ALBUQUERQUE NM 87185-0307
		2	DIR SNL R BRANNON MS 0820 M KIPP MS 0820 PO BOX 5800 ALBUQUERQUE NM 87185
		1	DSC PHILADELPHIA DSCP FNSE 2800 SOUTH 20TH ST PHILADELPHIA PA 19145-5099

<u>NO. OF COPIES</u>	<u>ORGANIZATION</u>
1	CDR NSWC MD11 DAHLGREN DIV 17320 DAHLGREN RD DAHLGREN VA 22448-5100
4	USSOCOM HQ USSOCOM SOAL T SAREN SOAL SP PULLAR COL KEENAN T MORRISSEY 7701 TAMPA PT BLVD MACDILL AFB FL 33621-5323
1	USSOCOM HQ USSOCOM ANNEX 501B M IVERSON 7701 TAMPA PT BLVD MACDILL AFB FL 33621-5323

ABERDEEN PROVING GROUND

1	US ARMY DEV TEST CTR CSTE DTC TT S T KOCHER 314 LONGS CORNER RD APG MD 21005
5	US ARMY ATC CSTE DTC AT CO COL BROWN (5 CPS) 400 COLLERAN RD APG MD 21005
15	US ARMY ATC CSTE DTC AT SL COL ELLIS (5 CPS) C VALZ (5 CPS) V W BLETHEN (5 CPS) 400 COLLERAN RD APG MD 21005
5	DIR USARL AMSRL WM J SMITH AMSRL WM TA W GOOCH W GILLICH W BRUCHEY AMSRL WM TD T HADUCH

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project(0704-0188), Washington, DC 20503.			
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE February 2002	3. REPORT TYPE AND DATES COVERED Final, April 1999-April 2001	
4. TITLE AND SUBTITLE Interceptor Small Arms Protective Insert (SAPI) MANTECH Product Enhancement Test Report II		5. FUNDING NUMBERS C: DAAN02-98-D-5007-009	
6. AUTHOR(S) Jeffrey A. Mears, [*] Robert F. Monks, [*] Robert Wolffe, [*] and James F. Mackiewicz [†]			
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Simula Safety Systems Inc. 7822 South 46th Street Phoenix, AZ 85044		8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army Natick Soldier Center AMSSB-RIP-MC(N) Natick, MA 01760-5011		10. SPONSORING/MONITORING AGENCY REPORT NUMBER ARL-CR-488	
11. SUPPLEMENTARY NOTES [*] Simula Safety Systems Inc., Phoenix, AZ 85044. [†] U.S. Army Natick Soldier Center, Natick, MA 01760-5011. The POC for this report is Dana Granville, USARL, ATTN: AMSRL-WM-MB, APG, MD 21005-5069.			
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.		12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) This report summarizes the work performed by Specialty Plastic Products of Pennsylvania Inc. and their subcontractor, Simula Safety Systems Inc., under the Manufacturing Technology (MANTECH) program sponsored by the U.S. Army Materiel Command and executed by the U.S. Army Natick Soldier Center. The objective of this effort was to investigate M Cubed Technologies Inc.'s siliconized silicon carbide armor material and process as an alternative ceramic component for the multi-Service Interceptor Small Arms Protective Inserts (SAPI).			
14. SUBJECT TERMS interceptor, SAPI, light armor, protective vest, composite armor		15. NUMBER OF PAGES 18	
		16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL

NSN 7540-01-280-5500

15

Standard Form 298 (Rev. 2-89)
Prescribed by ANSI Std. Z39-18 298-102

INTENTIONALLY LEFT BLANK.