

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.

1. REPORT DATE (DD-MM-YYYY)      2. REPORT TYPE  
Technical Papers      3. DATES COVERED (From - To)

4. TITLE AND SUBTITLE  
  
5a. CONTRACT NUMBER  
5b. GRANT NUMBER  
5c. PROGRAM ELEMENT NUMBER

*Please see attached*

6. AUTHOR(S)      5d. PROJECT NUMBER  
2302  
5e. TASK NUMBER  
MIG2  
5f. WORK UNIT NUMBER  
346120

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)  
Air Force Research Laboratory (AFMC)  
AFRL/PRS  
5 Pollux Drive  
Edwards AFB CA 93524-7048

8. PERFORMING ORGANIZATION REPORT

9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)  
Air Force Research Laboratory (AFMC)  
AFRL/PRS  
5 Pollux Drive  
Edwards AFB CA 93524-7048

10. SPONSOR/MONITOR'S ACRONYM(S)

11. SPONSOR/MONITOR'S NUMBER(S)  
*Please see attached*

12. DISTRIBUTION / AVAILABILITY STATEMENT  
  
Approved for public release; distribution unlimited.

13. SUPPLEMENTARY NOTES

14. ABSTRACT

20030129 224

15. SUBJECT TERMS

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT  A	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON Leilani Richardson
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (include area code) (661) 275-5015

2302 M162

MEMORANDUM FOR PRS (In-House Publication)

FROM: PROI (STINFO)

22 May 2002

SUBJECT: Authorization for Release of Technical Information, Control Number: **AFRL-PR-ED-VG-2002-125**  
C.T. Liu (PRSM) and J.N. Yang (UCI), "Investigating the Strain Rate Effect on the Critical Inherent Crack Size in a Particulate Composite Material"

**4<sup>th</sup> Int'l Conf on Statistical Mechanics**  
**(Corfu, Greece, 9-13 June 2002) (Deadline = 29 May 2002)**

**(Statement A)**

1. This request has been reviewed by the Foreign Disclosure Office for: a.) appropriateness of distribution statement, b.) military/national critical technology, c.) export controls or distribution restrictions, d.) appropriateness for release to a foreign nation, and e.) technical sensitivity and/or economic sensitivity.

Comments: \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

Signature \_\_\_\_\_ Date \_\_\_\_\_

2. This request has been reviewed by the Public Affairs Office for: a.) appropriateness for public release and/or b) possible higher headquarters review.

Comments: \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

Signature \_\_\_\_\_ Date \_\_\_\_\_

3. This request has been reviewed by the STINFO for: a.) changes if approved as amended, b) appropriateness of references, if applicable; and c.) format and completion of meeting clearance form if required

Comments: \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

Signature \_\_\_\_\_ Date \_\_\_\_\_

4. This request has been reviewed by PR for: a.) technical accuracy, b.) appropriateness for audience, c.) appropriateness of distribution statement, d.) technical sensitivity and economic sensitivity, e.) military/national critical technology, and f.) data rights and patentability

Comments: \_\_\_\_\_  
\_\_\_\_\_

APPROVED/APPROVED AS AMENDED/DISAPPROVED

\_\_\_\_\_  
PHILIP A. KESSEL Date  
Technical Advisor  
Space and Missile Propulsion Division

# Investigating the Strain Rate Effect on the Critical Inherent Initial Crack Size in a Particulate Composite Material

C. T. Liu

Principal Research Engineer


PRSM


Air Force Research Laboratory

J.N. Yang

Dept. of Civil Engineering

University of California at Irvine

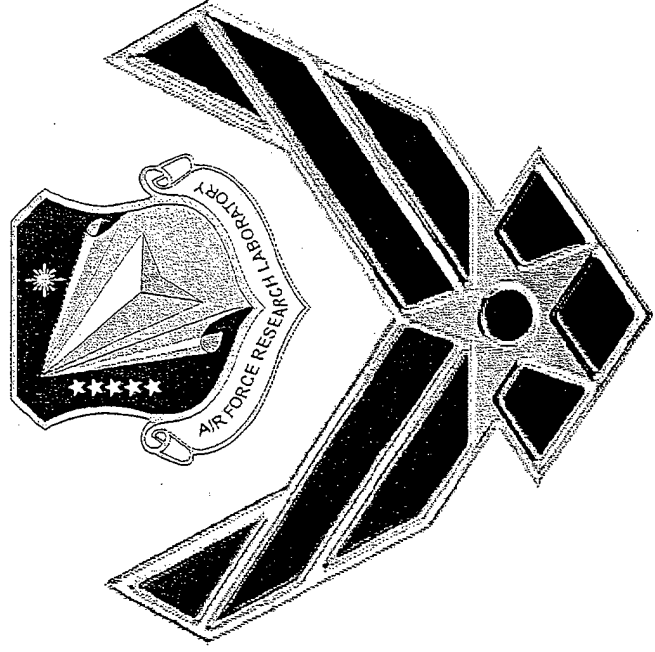






# Objectives




- Investigate the Effect of Strain Rate on the Critical Inherent Crack Size in a Particulate Composite Material
  - Strain Rates: 0.727 In/in/mm. 18.18 In/in/mm
- Determine the Statistical Distribution Function of the Critical Inherent Crack Size
  - Normal Distribution
  - Two-Parameter Lognormal Distribution
  - Two-Parameter Weibull Distribution
  - Second Asymptotic Distribution of Maximum Value






# Maximum Stress Versus Maximum Time

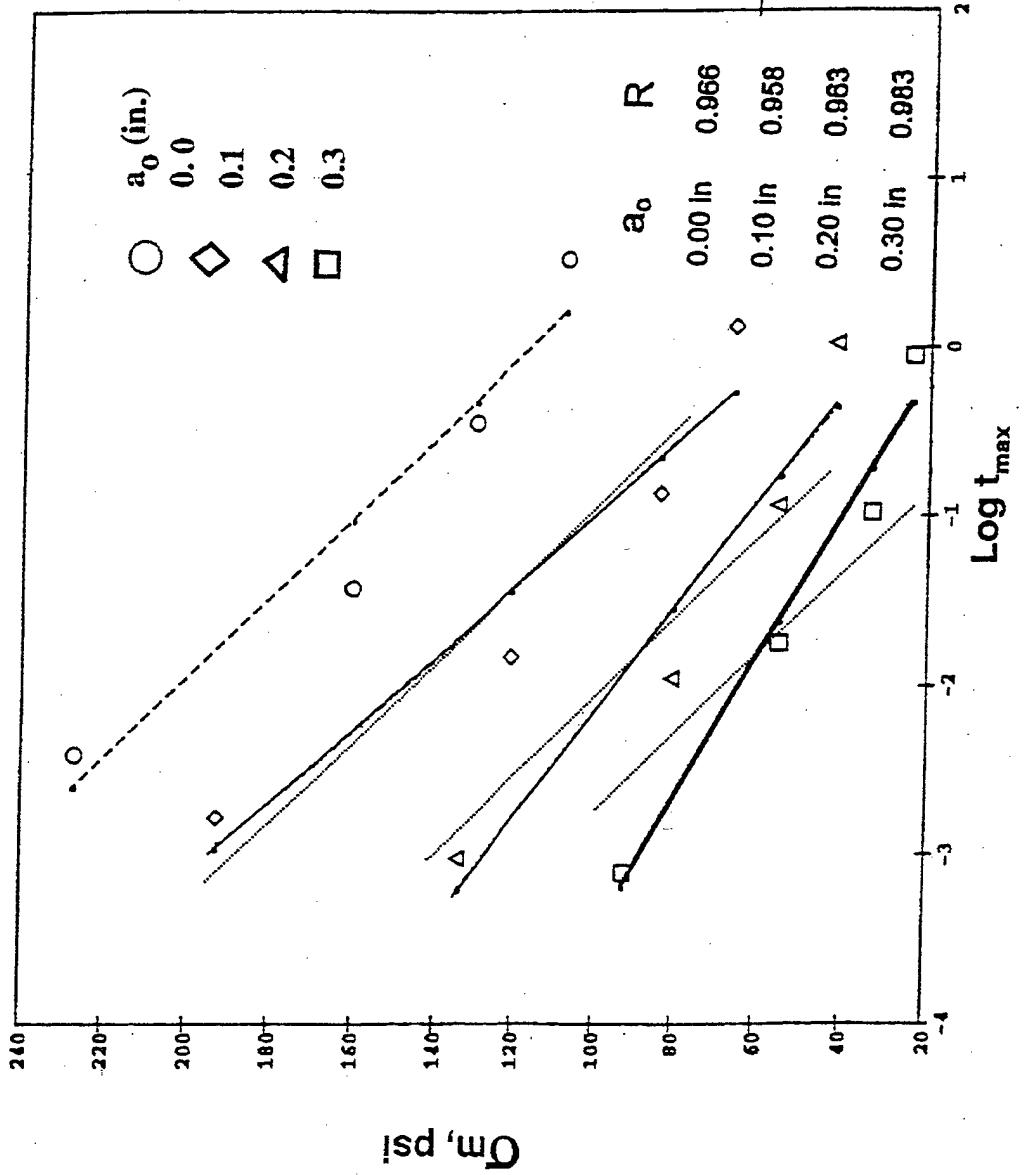




# Cracked Specimen

(Displacement Rate = 50 in/min)

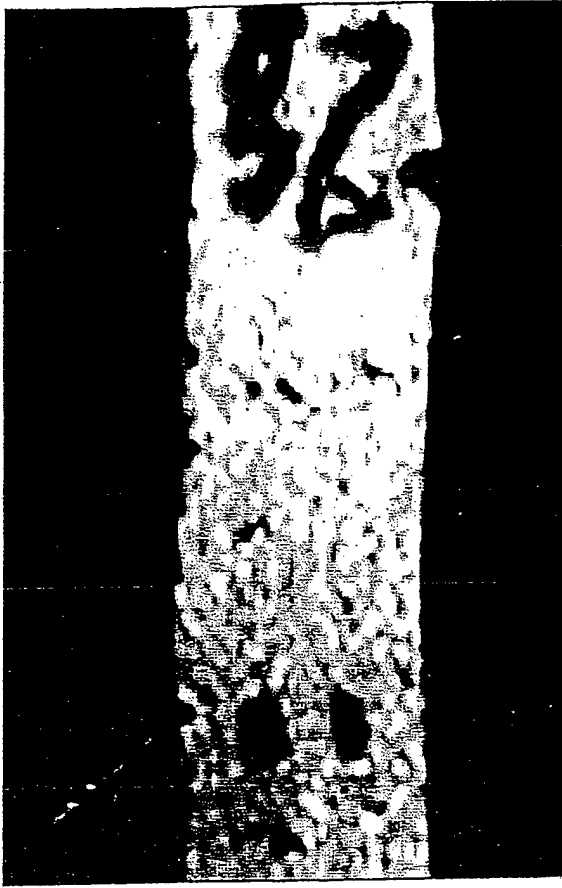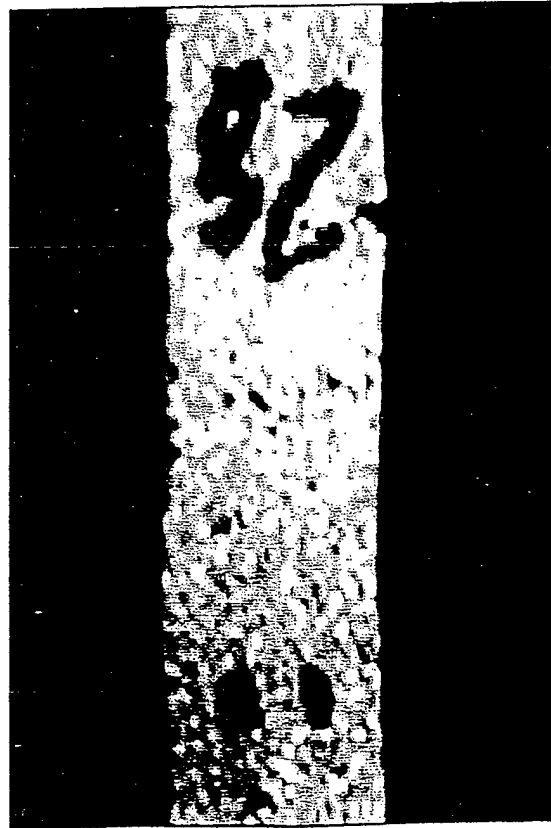




## Distribution Parameters for Normal, Two-Parameter Lognormal, Two-Parameter Weibull, and Second Asymptotic Distribution of Maximum Value



- Displacement Rate = 50 in/min

Mean $\mu$ (in.)	0.15750	0.14735	0.14597
Standard Deviation $\sigma$ (in.)	0.00290	0.00296	0.00290
Coefficient of Variation $v = \sigma/\mu$	0.01843	0.02008	0.01989
$\mu^* = \ln [\mu / (1+V^2)^{1/2}]$	-1.84850	-1.91515	-1.92455
$\sigma^* = [\ln(1+V^2)]^{1/2}$	0.01843	0.02008	0.01989
$\alpha$	53.6679	49.6042	50.0732
$\beta$	0.1590	0.1488	0.1474
$\kappa$	51.3792	47.7947	48.4204
$\nu$	0.1559	0.1458	0.1444




## Distribution Parameters for Normal, Two-Parameter Lognormal, Two-Parameter Weibull, and Second Asymptotic Distribution of Maximum Value




- Displacement Rate = 2 in/min

	$a_c$	$a^*$	$a_0$
Mean $\mu$ (in.)	0.12999	0.12131	0.11865
Standard Deviation $\sigma$ (in.)	0.00152	0.00159	0.00157
Coefficient of Variation $V = \sigma/\mu$	0.01172	0.01315	0.01324
$\mu^* = \ln [\mu / (1+V^2)^{1/2}]$	-2.04037	-2.10949	-2.13166
$\sigma^* = [\ln(1+V^2)]^{1/2}$	0.01172	0.01315	0.01324
$\alpha$	80.1490	74.4797	74.4295
$\beta$	0.1308	0.1221	0.1194
$\kappa$	72.4144	70.8220	71.9862
$\nu$	0.1291	0.1204	0.1178




CSM Liu.ppt

# Summary of Crack Lengths (Displacement Rate = 2 in/min)



	$a_c$	$a^*$	$a_0$
Specimen 1	0.12965	0.12968	0.11793
Specimen 2	0.12964	0.12030	0.11753
Specimen 3	0.12918	0.12052	0.11790
Specimen 4	0.12966	0.12046	0.11778
Specimen 5	0.12608	0.11785	0.11545
Specimen 6	0.13168	0.12287	0.12012
Specimen 7	0.13145	0.12338	0.12084
Specimen 8	0.13069	0.12171	0.11902
Specimen 9	0.13057	0.12281	0.12029
Specimen 10	0.13100	0.12256	0.11988
Specimen 11	0.13029	0.12124	0.11846

$a_c$  is the critical crack length,  $a^*$  is the predicted critical inherent crack  
The critical crack length  $a_c$  is the predicted critical inherent crack length




CSM Group

## Summary of Crack Lengths (Displacement Rate = 50 in/min)





	$a_c$	$a^*$	$a_0$
Specimen 1	0.15425	0.14396	0.14258
Specimen 2	0.15425	0.14396	0.14258
Specimen 3	0.15543	0.14530	0.14386
Specimen 4	0.15993	0.15018	0.14888
Specimen 5	0.15268	0.14237	0.14114
Specimen 6	0.15476	0.14506	0.14379
Specimen 7	0.15505	0.14471	0.14348
Specimen 8	0.15073	0.15029	0.14883
Specimen 9	0.16006	0.14973	0.14826
Specimen 10	0.15765	0.14717	0.14575
Specimen 11	0.15902	0.14858	0.14711
Specimen 12	0.16086	0.15115	0.14976
Specimen 13	0.15963	0.14965	0.14819




CSM Liu.ppt

# Normal Distribution Plot for $a_0$

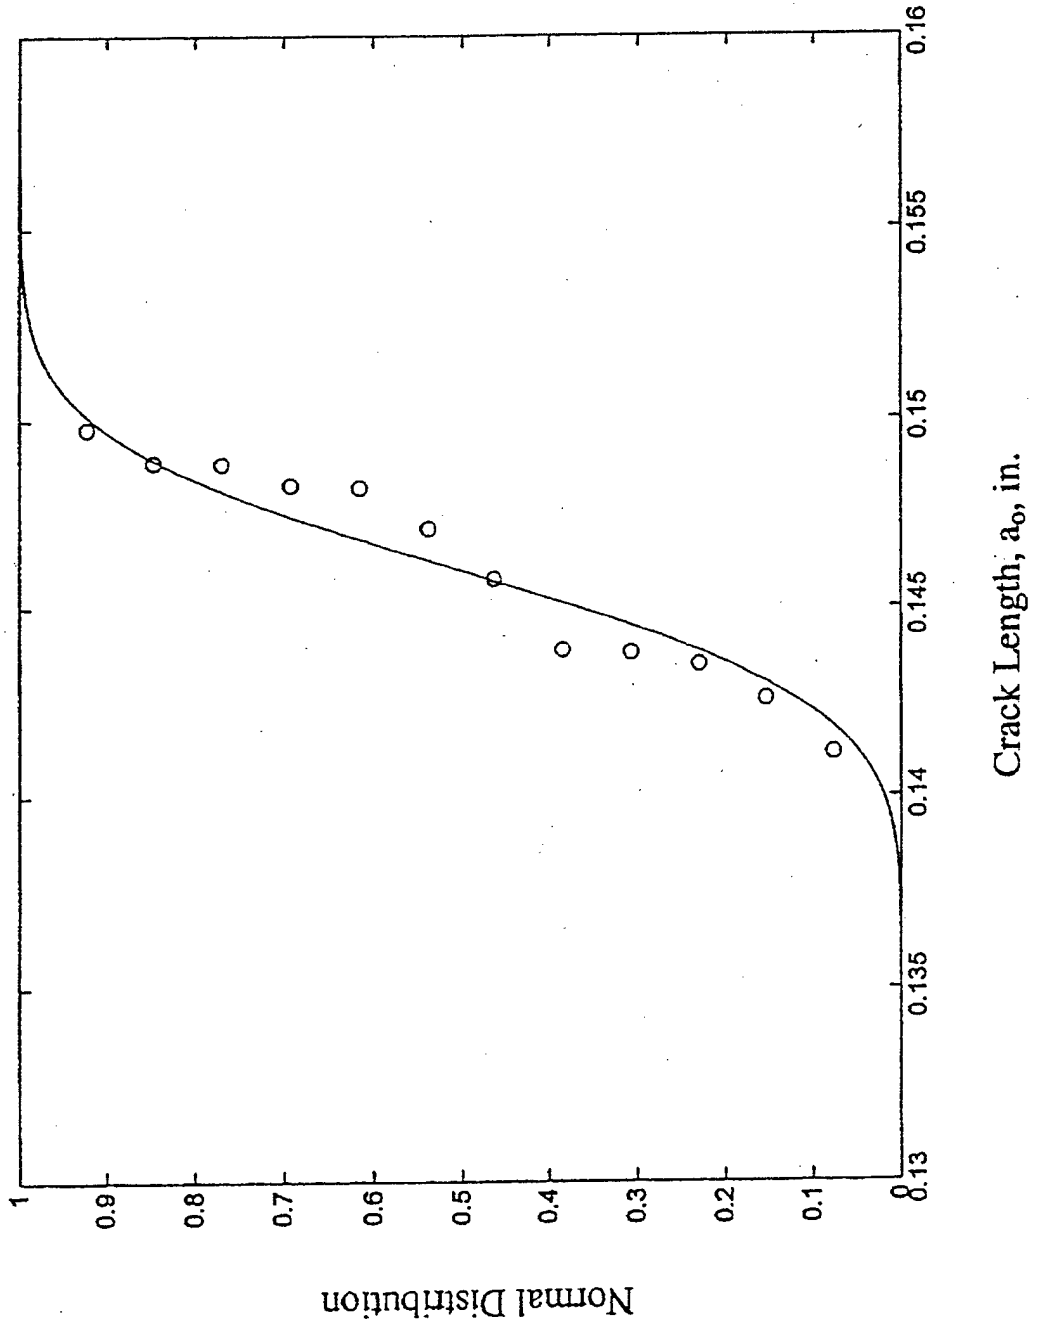





# Two-Parameter Lognormal Distribution Plot for $a_0$

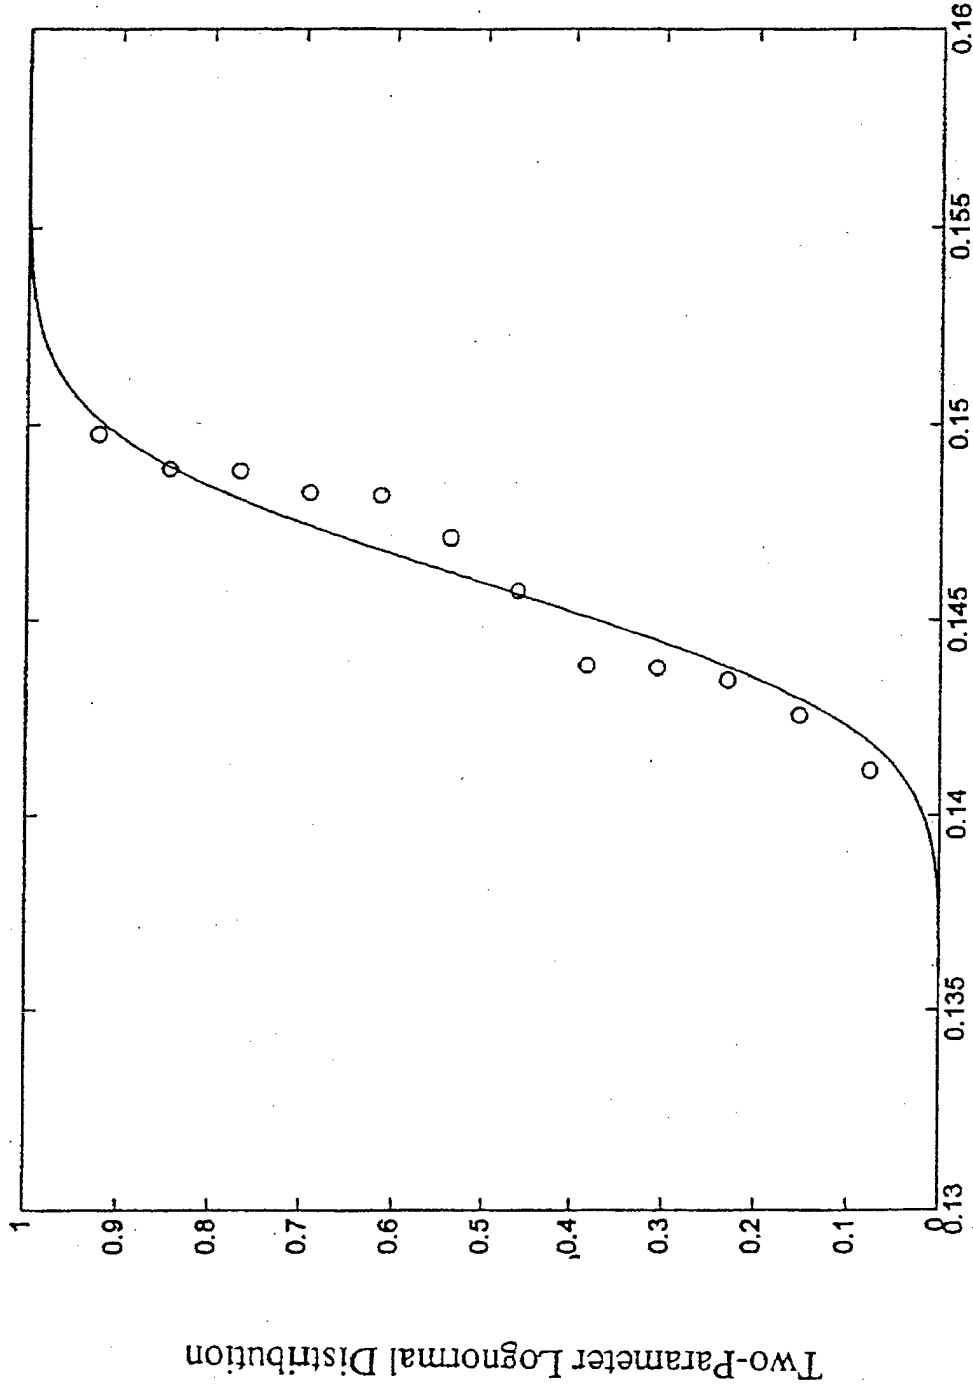


Crack Length,  $a_0$ , in.





# Two-Parameter Weibull Distribution Plot for $a_0$

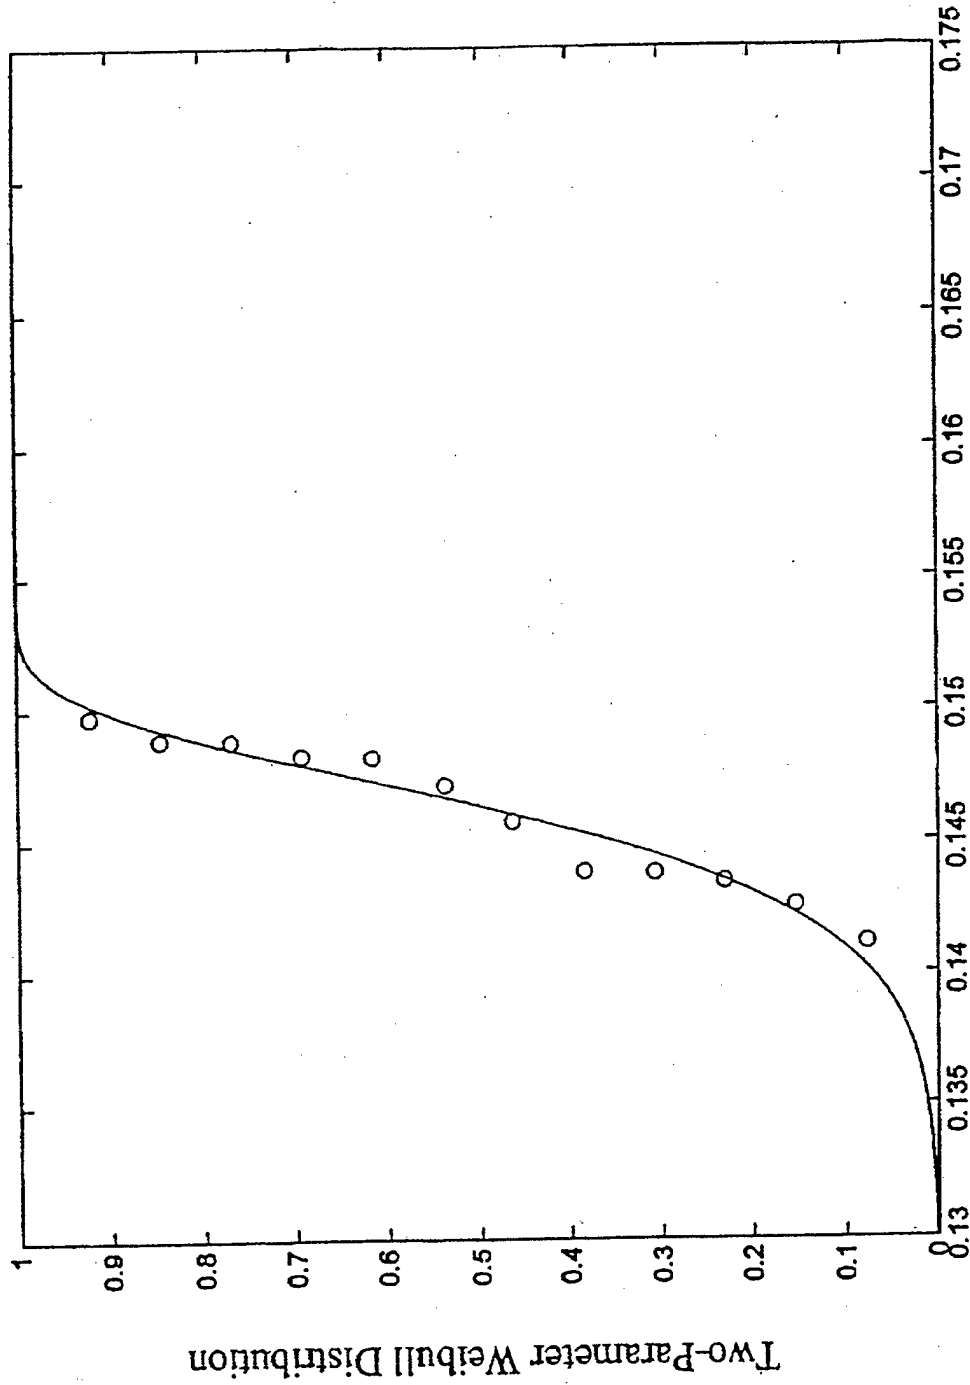


Crack Length,  $a_0$ , in.



# Second Asymptotic Distribution of Maximum Value Plot for $a_0$

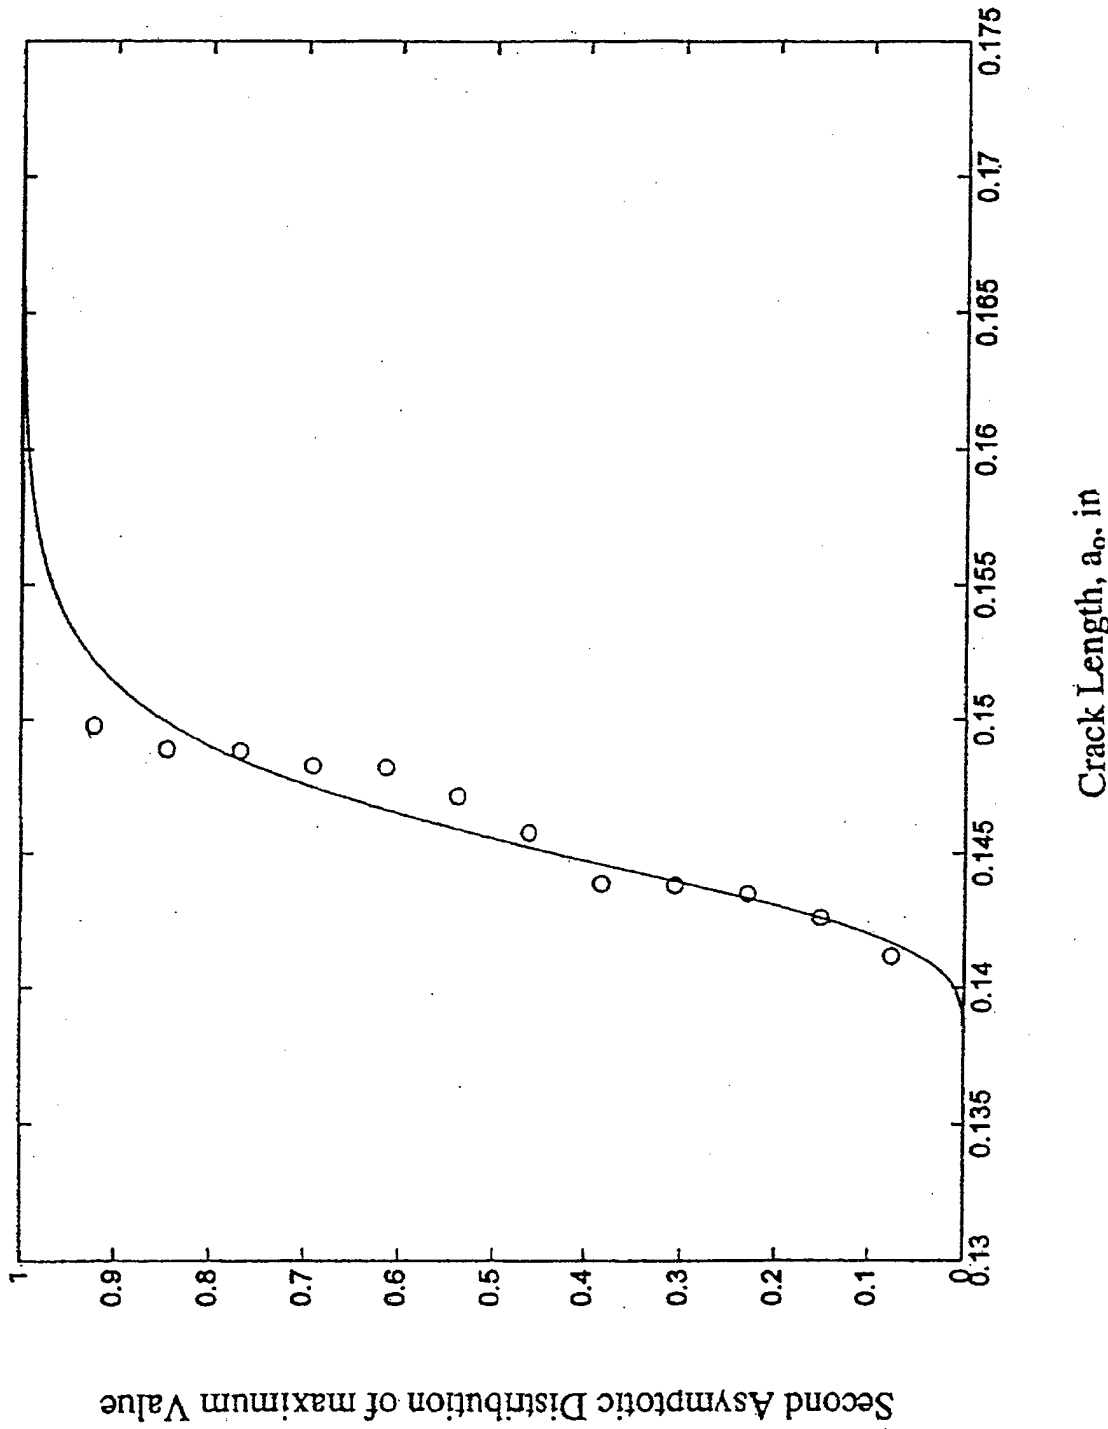



## Conclusions



- For the material studied, strain rate has no significant effect on the critical inherent crack size
- The predicted average critical inherent crack size is 0.132, which compares well with experimental value
- The critical inherent crack size follows the Two-Parameter Weibull Distribution