

REPORT DOCUMENTATION PAGE

Form Approved
OMB NO. 0704-0188

Public Reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comment regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave Blank)		2. REPORT DATE July 31, 2002	3. REPORT TYPE AND DATES COVERED Final Report: Aug. 1, 1998-Jul. 31, 2002	
4. TITLE AND SUBTITLE Fabrication of High-Performance Coatings Systems Via a Novel In-Situ/Ex-Situ Characterization Technique			5. FUNDING NUMBERS DAAG 55-98-1-0382	
6. AUTHOR(S) J. C. Bilello				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Department of Materials Science & Engineering University of Michigan Ann Arbor, MI 48109-2136			8. PERFORMING ORGANIZATION REPORT NUMBER UM-ARO 2002-110	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) U. S. Army Research Office P.O. Box 12211 Research Triangle Park, NC 27709-2211			10. SPONSORING / MONITORING AGENCY REPORT NUMBER 37716.6-MS	
11. SUPPLEMENTARY NOTES The views, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy or decision, unless so designated by other documentation.				
12 a. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution unlimited.			12 b. DISTRIBUTION CODE See DoDD 4230.25, "Distribution Statements on Technical Documents"	
13. ABSTRACT (Maximum 200 words) This report will briefly outline some of the key findings made during the course of this project and some new work on the phase structure changes concomitant with the delamination behavior of Ta metallizations. Detailed accountants of prior work have been included in previous "Interim Reports" of this Grant and in the many technical papers that have resulted from the support of this work. A complete list of these publications in provided in Appendix II of this Final Report.				
14. SUBJECT TERMS Thin Films, High Temperature Ta coatings, Residual Stress, Coating Delamination, X-ray imaging			15. NUMBER OF PAGES 20 pages (inc. Appendices)	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OR REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION ON THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

NSN 7540-01-280-5500

Standard Form 298 (Rev.2-89)
Prescribed by ANSI Std. Z39-18
298-102

Enclosure 1

20030602 070

FABRICATION OF HIGH-PERFORMANCE
COATINGS SYSTEMS VIA A NOVEL
IN-SITU/EX-SITU CHARACTERIZATION TECHNIQUE

FINAL REPORT:
JULY 31, 2001

by

John C. Bilello

U.S. ARMY RESEARCH OFFICE
Program Manager: Dr. William Lampert,
Materials Science Division

GRANT NUMBER: DAAG 55-98-1-0382

University of Michigan
Department of Materials Science and Engineering
Ann Arbor, Michigan 48109-2136

APPROVED FOR PUBLIC RELEASE:
DISTRIBUTION UNLIMITED

THE VIEWS, OPINIONS, AND/OR FINDINGS CONTAINED IN THIS REPORT ARE
THOSE OF THE AUTHOR(S) AND SHOULD NOT BE CONSTRUED AS AN OFFICIAL
DEPARTMENT OF THE ARMY POSITION, POLICY, OR DECISION, UNLESS SO
DESIGNATED BY OTHER DOCUMENTATION.

FABRICATION OF HIGH-PERFORMANCE
COATINGS SYSTEMS VIA A NOVEL
IN-SITU/EX-SITU CHARACTERIZATION TECHNIQUE

Final Grant Report: July 2002

By

John C. Bilello

Abstract

This report will briefly outline some of the key findings made during the course of this project and some new work on the phase structure changes concomitant with the delamination behavior of Ta metallizations. Detailed accountants of prior work have been included in previous "Interim Reports" of this Grant and in the many technical papers that have resulted from the support of this work. A complete list of these publications is provided in Appendix II of this Final Report.

FINAL REPORT: July 31, 2002

By John C. Bilello

Overview:

During the four years that this project has run a number of significant milestones have been reached. This Final Project report will not repeat the details of this work, which has been previously reported in previous "Interim Project Reports" and the numerous publications that are listed in the Appendix II of this paper. This report will concentrate on the highlights and include some new work done in the last eight months of the Grant, i.e. since the last Interim Report. Research focused on Ta refractory metal films.^{1,2,3,4,5} The key development of this Grant was the construction, commissioning and ultimate utilization in thermo-mechanical testing of a novel *in situ* real-time synchrotron topography imaging facility. This equipment is has proven capable of examining the debonding limits of a number of refractory metal high temperature coatings. These observations have been coupled with real-time high resolution Bragg scattering studies to elucidate the concomitant phase and chemical structure of the film relating to the observed delamination modes. Finally, we will discuss some directions this work has pointed that would be worthy of future investigation.

Experimental Methods:

A detailed report on the novel *in situ* real-time x-ray imaging stage and some experiments utilizing its capabilities has been given in previous references.^{6,7} This stage has been upgraded to go to slightly higher temperatures (600C vs. 550C) and has been fitted with a temperature controller so that a variety of temperatures can be easily programmed into its test performance.⁸ Figure 1 shows the capability of this control to be able to achieve a range of steady temperatures with variable ramp rates. This feature will allow future work that can accurately measure kinetic behavior by studies time dependent relaxation behavior as a function of temperature.

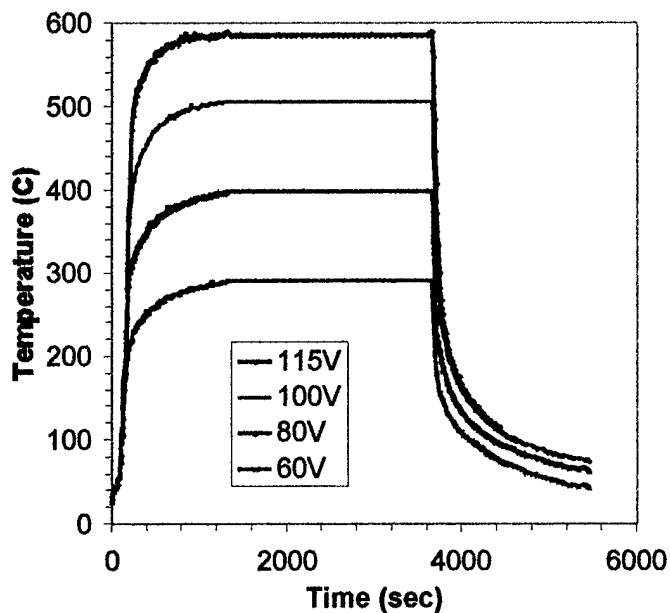


Figure 1

Variable temperature control of the *in situ* real-time synchrotron thermomechanical topography/radiography imaging stage.

We have also used our high resolution high energy 18kW Rigaku laboratory source, built under an earlier DARPA Grant, to observe

Bragg diffraction of thin Ta films as a function of time and temperature. By this means we were able to correlate the chemical phase structure of the films to their thermomechanical behavior.

Results and Discussion:

It may be recalled that in an earlier report it was shown that there was a critical working gas pressure that marked the region between adherent Ta films and those that rapidly debonded. Partial results were shown in the previous progress report (reference 2) and further work has been in the intervening period and is shown below in Table 1.

Argon Pressure (mTorr)	Degree of Blistering	Spalling?
2	Major	Yes
3	Major	Yes
5	Major	Yes
6	Minor	No
7	Minor	No
8	None	No
10	None	No
15	None	No
18	None	No

Table 1

Observed film delamination modes as a function of Ar working gas pressure during sputter deposition.

It is interesting (and significant) to note that no debonding was observed of any type when these films were subjected to high temperature testing in an oxygen environment. Why? Obviously, we wouldn't ask this question if we didn't have some inkling about what is happening. To clarify the behavior a series of Bragg scattering experiments were done as a function of time on a 600nm Ta film held at 600C at ambient.⁹ The results are reported below in Figure 3.

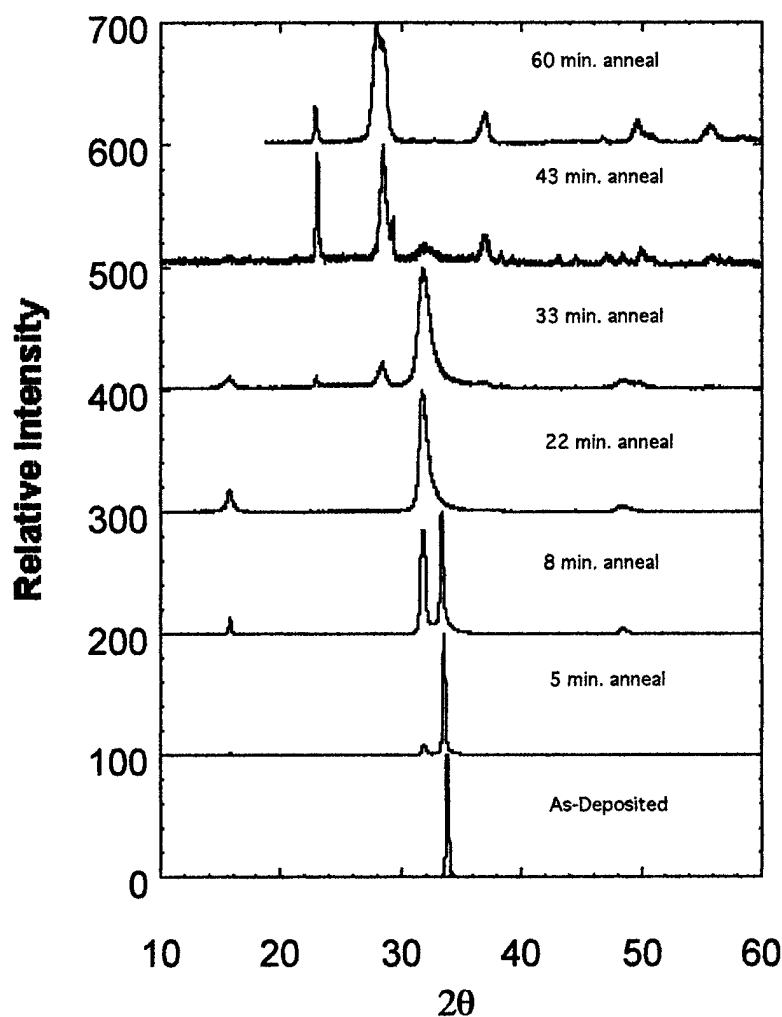


Figure 3 - Diffraction patterns at various times of a 600nm Ta film deposited at 2 mTorr Ar and annealed in ambient environment at 600C. Note the appearance of distinctive diffraction lines at various times - details explained in the text.

The initial "as deposited" diffraction plot shows a strong *out-of-plane* texture, hence the single intensive peak indicative of beta Tantalum. As the annealing procedures when 22 minutes is reached the film is seen to be converting to an unknown oxide (i.e. one not found in JCPDS files). Finally, by the 43 minute mark the film has converted to Tantalum pentoxide (Ta_2O_5). The next step was to correlate these findings directly with the morphology of these films as they are undergoing these phase transformations. This is displayed in Figure 4 below.

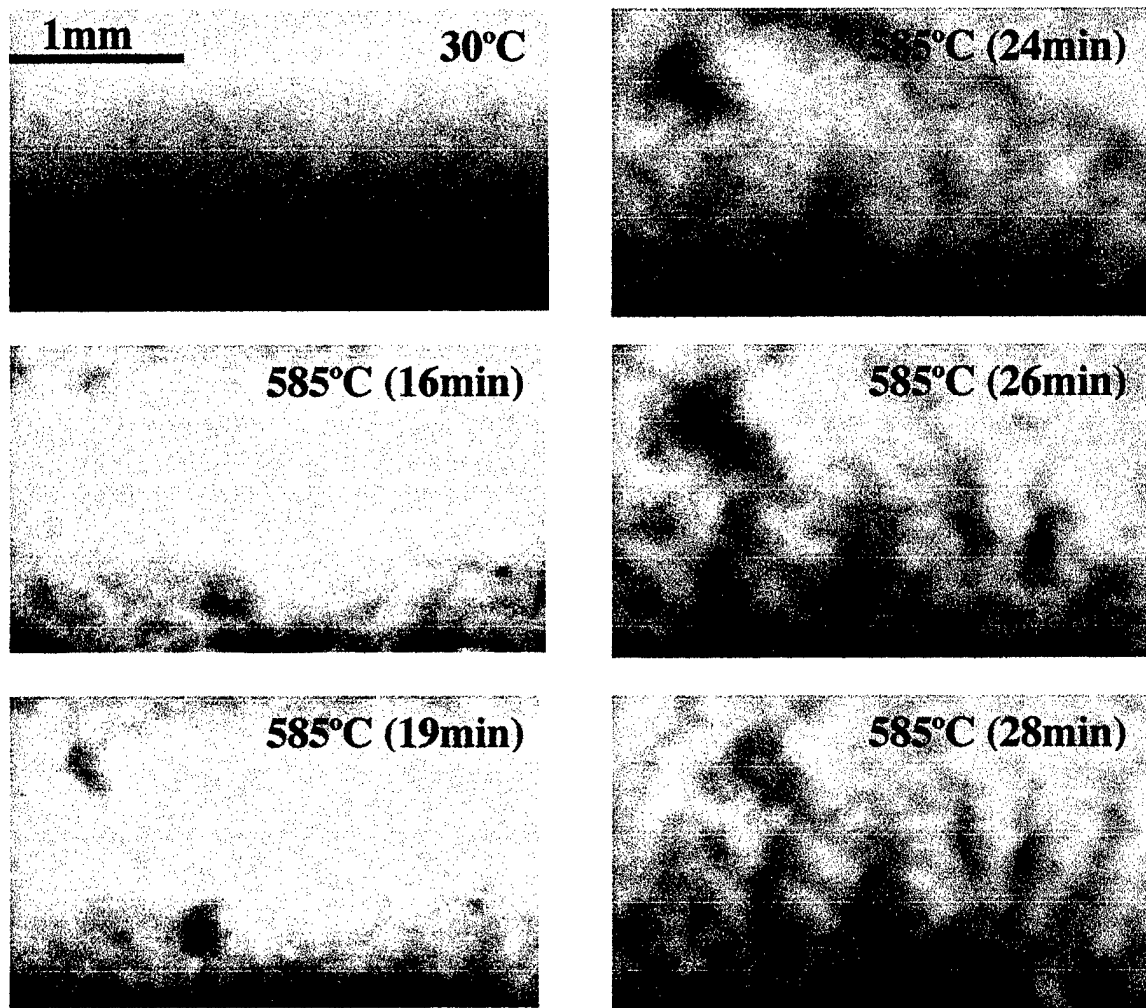


Figure 4 - Morphology of Ta films as a function of time annealed in ambient at 585C.

The small difference in temperature between the annealing run used for Bragg diffraction (Figure 3) and for the observed diffraction Topography/Radiography images is do to a slight mismatch in the calibration of the controllers on the two different instruments. Nevertheless the picture emerges that the film starts to blister, hence nucleating subsequent complete delamination effects, when the initial β -Ta deposition converts to an oxide. But the story isn't this simple. Subsequent annealing/Bragg diffraction experiments on Ta films grown in the high pressure Ar regime that exhibited no delamination and excellent adhesion showed the same phase transformation sequence as a function of time. This leads us to suspect that the real culprit here controlling delamination is the stress induced by the coefficient of thermal expansion (CTE) between the growing oxide phase in the transformation and the substrate. The films deposited at higher Ar working gas pressures are nominally less dense than those grown at lower pressures. This more open structure is probably able to accommodate the CTE mismatch strains and remain intact. If this is true it might provide a potent recipe for growing Ta (and perhaps other refractory films) in a manner that can enhance their thermo-mechanical stability. How to prove this supposition? What is needed is an in situ method of simultaneously measuring the strain (stress state) in the films as a function of time a temperature. Also parallel studies using Transmission Electron Microscopy (cross-section mode) to study the interfaces at adhesive and decohesive regions of the films are of interest. The ability of synchrotron diffraction topography/radiography to find critical regions is critical to these

subsequent experimental plans. These areas will be explored as part of a new program sponsored by ARO in the future.

Summary:

A novel new method for directly observing the thermo-mechanical response of refractory metal coatings has been developed. This technique relies on a thermo-mechanical stage capable of *in situ* real-time imaging of the mechanical behavior of film overlays on a high intensity synchrotron beam line. This facility has been able to take action sequence x-ray images at a rate of 30/sec at temperatures as high as 600C and record the film response to the thermo-mechanical conditions imposed.

The x-ray images of the morphology of the films as a function of time and temperature in an oxidizing environment (ambient) has been supplemented by time dependent Bragg diffraction studies of the chemical phase structure of the films. The results have shown that the β -Ta films eventually converts to Ta_2O_5 upon annealing, which could induce a critical CTE mismatch leading to film failure if not properly accommodated by the film microstructure.

References:

¹ S. L. Lee, M. Cipollo, D. Windover, and C. Rickard, Surface and Coatings Technology 120-121, 44 (1999).

² M. Stavrev, D. Fischer, C. Wenzel, K. Drescher, and N. Mattern, Thin Solid Films 307, 79 (1997).

³ C. Cabral, Jr., L. A. Clevenger, and R. G. Shad, *Mat. Res. Soc. Symp. Proc.* 308, 57 (1993).

⁴ L. A. Clevenger, A. Mutscheller, J. M. E. Harper, C. Cabral, Jr., and K. Barmak, *J. App Phys.* 72 (10), 4918 (1992).

⁵ N. R. Moody, R. Q. Hwang, S. Verka-Taraman, J. E. Angelo, D. P. Norwood, and W. W. Gerberich, *Acta mater.* 46 (2), 585 (1998).

⁶ Z. B. Zhao, Z. U. Rek and J. C. Bilello, *Phil. Trans. Royal Soc. Lond. A*, 357, (1999), p. 2681.

⁷ ARO Interim Progress Report, GRANT NUMBER: DAAG 55-98-1-0382, January 1, 2001 to December 31, 2002.

⁸ B. L. French and J. C. Bilello, *Real-time In Situ Imaging of the "Delamination of Thin Ta Films on Si (100) Substrates via a Synchrotron Radiation Technique*, Eds. By C. S. Ozkan, L. B. Freund, R. C. Cammarata, and H. Gao, *MRS Symp. Proc.* 695, 385, (2002).

⁹ B. L. French, M. J. Daniels, and J. C. Bilello, *Correlation of stress and phase evolution of thin Ta films on Si (100) during thermal testing*, Materials Research Society Fall Meeting, Symposium Y, Boston, MA, Dec. 4, 2001.

Appendix I

Awards

John C. Bilello, Awarded a Senior NATO Visiting Fellowship to the Department of Materials, Oxford University, Oxford, United Kingdom, (2001). Renewed 2002-2004

John C. Bilello, Appointed Department Fellow, Department of Materials, Oxford University, Oxford, United Kingdom, (2001 and 2002).

Appendix II

PUBLICATIONS AND OF SCHOLARLY ACTIVITY: (Through Grant completion date - July 31, 2001)

Publications in Refereed Journals and Books:

J. F. Whitacre, Z. U. Rek, S. M. Yalisove, and J.C. Bilello, *Phase Content and Stress State in Sputtered Nanoscale Ta/Ta₂O₅ Films*, to be submitted to *Thin Solid Films* (2002).

Z. B. Zhao, S. M. Yalisove, Z. U. Rek and J. C. Bilello, Evolution of Anisotropic Microstructure and Residual Stress in Sputtered Cr Films, *Jour. Applied Physics*, 92, (2002), 7183.

Z. B. Zhao, J. Herschberger, S. M. Yalisove, and J. C. Bilello, *Determination of Residual Stress in Thin Films: A Comparative Study of X-ray Topography versus Laser Curvature Method*, *Thin Solid Films*, 415, (2002), 21-31.

B. L. French and J. C. Bilello, *Real-time in situ Imaging of the Delamination of Thin Ta Films on Si(100) Substrates via a Synchrotron Radiation Techniques*, *Mat. Res. Soc. Symp. On Thin Films - Stresses and*

Mechanical Properties IX, Accepted for Publication (2002) MRS Proceedings, in Press.

M. J. Daniels, J. Maciejewski, J. S. Zabinski, Z. U. Rek, S. M. Yalisove, and J. C. Bilello, *An Investigation of Sputtered Al-Cu-Fe-Cr Quasicrystalline Films via Synchrotron Diffraction*, Mat. Res. Soc. Symp. Vol. 643, (2001), K8.4.1

M. J. Daniels and J. C. Bilello, *Characterization of Nanoscale Materials Structures via High Resolution Synchrotron Scattering, Nano-technology*, Eds. M. A. Fortes and P. J. Ferreira, IST Press, Lisbon, Portugal, (2001), Chapter in Book.

M. J. Daniels, J.C. Bilello, D. Hyland, D. Dew-Hughes, C.R.M. Grovenor, *High Resolution X-ray Characterization of Tl-2212 Superconducting Thin Films*, Mat. Res. Soc. Symp. Vol. 678, (2001), EE2.5.1.

J. F. Whitacre, S. M. Yalisove & J. C. Bilello, *Real-time/In-situ Diffraction Study of Phase and Microstructural Evolution in Sputtered beta Ta/Ta₂O₃ Films*, J. Vac. Soc. & Tech. A 19(6), (2001), 2910.

L. P. Kendig, Z. U. Rek, S. M. Yalisove, J. C. Bilello, *Role of impurities and microstructure on residual stress in nanoscale Mo films*, Surface Coatings and Technology, 132, 124 (2000).

J. F. Whitacre, J. C. Bilello and S. M. Yalisove, *In-Plane Texturing in Films and Coatings*, Textures and Microstructures, Textures and Micro-structures, TMS, Pittsburgh, PA, 34, 91 (2000).

J. F. Whitacre, S. M. Yalisove and J. C. Bilello, *Deposition Kinetics and Microstrutural Evolution in Sputtered Ta Films: A Real-Time/In Situ Study*, Mat. Res. Soc. Symp. on Polycrystalline Metal and Magnetic Thin Films, Published Proceedings MRS, (1999).

Z. B. Zhao, Z. U. Rek and J. C. Bilello, *Observation of the adhesion of thin Ta polycrystalline films to Si wafers via in situ topography/radiography*, Phil. Trans. Royal Soc. Lond. A, 357, (1999), p. 2681.

- A. K. Malhotra, J. F. Whitacre, Z. B. Zhao, J. Hershberger, S. M. Yalisove and J. C. Bilello, *An In-situ/Ex-situ X-ray Analysis System for Thin Sputtered Films*, *Surface and Coating Tech.*, 110, (1998), 105-110.
- J. F. Whitacre, Z. U. Rek, J. C. Bilello and S. M. Yalisove, *Surface Roughness and In-Plane Texturing in Sputtered Thin Films*, *J. Appl. Phys.* 84, (1998), 1346-1353.
- Z. B. Zhao, J. G. Hershberger, S. M. Yalisove and J. C. Bilello, *On the Measurement of Residual Stress in Thin Films*, *Mat. Res. Soc. Symp: Stress and Mechanical Properties in Thin Films*, Vol. 505, (1998), 519-525.
- Z. B. Zhao, J. G. Hershberger, A. Chiaramonti, Z. U. Rek and J. C. Bilello, *Real-time In Situ Diffraction Topography Imaging of Deformation*, *Mat. Res. Soc. Proceedings, Symp. - Application of Synchrontron Radiation in Materials Science*, Vol. 502, (1998), 163-169.
- J. F. Whitacre, Z. U. Rek, J. C. Bilello and S. M. Yalisove, *Probing Stress State and Phase Content in Ultra-Thin Ta Films*, *Mat. Res. Soc. Proceedings, Symp.*, *Mat. Res. Soc. Symp. Proc, Applications of synchrotron radiation to materials science*, Vol. 524, (1998), 115-119.
- Z. B. Zhao, J. G. Hershberger, A. Chiaramonti, Z. U. Rek, J. C. Bilello, *Real Time In-Situ Studies Of Deformation Processes Of Metallic Crystals And Thin Films Via X-ray Topography*, *Mat. Res. Soc. Symp.* Vol. 524, 81(1998).
- J. Hershberger, F. Kustas, Z. U. Rek, S. M. Yalisove and J. C. Bilello, *Degree of Crystallinity and Strain in B₄C and SiC thin films as a function of processing conditions*, *Mat. Res. Soc. Proceedings, Symp.*, *Application of Synchrotron Radiation Techniques to Materials Science*, in press, Spring, Vol. 524, (1998), 109-114.
- J. Hershberger, F. Kustas, Z. U. Rek, S. M. Yalisove and J. C. Bilello, *Structure determination of B₄C and SiC thin films via synchrotron high-resolution diffraction*, *Mat. Res. Soc. Symp. - Thin Films-Stresses and Mechanical Properties*, Vol. 505, (1998), 635-640.

O. P. Karpenko, J. C. Bilello, and S. M. Yalisove, *Growth Anisotropy And Self-Shadowing: A Model For The Development Of In-Plane Texture During Polycrystalline Thin-Film Growth*, J. Appl. Phys. 82:3 (1997) 1397-1403.

S. G. Malhotra, Z. U. Rek, S. M. Yalisove and J. C. Bilello, *Analysis Of Thin Film Stress Measurement Techniques*, Thin Solid Films, 301 (1997) 45-54.

S. G. Malhotra, Z. U. Rek, S. M. Yalisove, J. C. Bilello, *Depth-Sensitive Strain Analysis Of A W-Ta-W Trilayer*, Thin Solid Films 301, (1997) 55-61.

S. G. Malhotra, Z. U. Rek, S. M. Yalisove; J. C. Bilello, *Strain Gradients And Normal Stresses In Textured Mo Thin Films*, J. Vac. Sci. Technol. A, 15 (1997) 345-352.

L. J. Parfitt, Z. U. Rek, S. M. Yalisove and J. C. Bilello, *Native Oxide and the Residual Stress of Thin Mo and Ta Films*, Accepted for publication: MRS Symposium Proceedings on: Thin Films: Surfaces and Morphology eds, R. Cammorata, T. Einstein, E. Chasen and E. Williams, Vol. 441, (1997).

Reports

John C. Bilello, "Advanced Tribological Coatings", Renewal Report to Stanford Synchrotron Radiation Laboratory, (2002), SSRL no. 2592.

M.J. Daniels, Z.U. Rek, and J.C. Bilello, *Phase Determination for Enhancement of Tribological Properties in the Al-Cu-Fe-Cr Quasicrystalline System*, Stanford Synchrotron Radiation Laboratory Activity Report, (2000), Proposal 2592.

J. Mirecki Millunchick, S. Manville, C. Dorin, Z. U. Rek, and J. C. Bilello, *A Study of III-V Compound Semi-conductor Thin Films Using Synchrotron Topography*, Stanford Synchrotron Radiation Laboratory Activity Report, (2000), Proposal 2652.

J.F. Whitacre, Z.U. Rek, S.M. Yalisove & J.C. Bilello, *Structure and Phase in Nanoscale Ta/Ta₂O₅ Films Via Grazing Incidence X-ray Scattering*, Stanford Synchrotron Radiation Laboratory Activity Report, (2000), Proposal No. 2592.

B.A. Rainey, A. Mehta*, S.M. Yalisove, and J.C. Bilello, *A Study of Chromium Nitride Thin Films Using High-Resolution Synchrotron Diffraction*, Stanford Synchrotron Radiation Laboratory Activity Report, (2000), Proposal No. 2592.

J.F. Whitacre, Z.U. Rek, S.M. Yalisove and J.C. Bilello, *Amorphous Content in Thin Ta Films Via Grazing Incidence X-ray Scattering Phase and Stress State in Ultra Thin Ta Films Via Grazing Incidence X-Ray Scattering*, Stanford Synchrotron Radiation Laboratory Activity Report, (1998), Proposal 2346MP.

J. Hershberger, Z. U. Rek, S. M. Yalisove, and J. C. Bilello, *Development of stress, morphology, and structure in B₄C thin films*, Stanford Synchrotron Radiation Laboratory Activity Report, (1998), Proposal 2346MP

J. Hershberger, Z. U. Rek, S. M. Yalisove, and J. C. Bilello, *Strain in Mo Buried Layers*, Stanford Synchrotron Radiation Laboratory Activity Report, (1998), Proposal 2346MP.

Z. B. Zhao, S. M. Yalisove, Z. U. Rek and J. C. Bilello, *Analysis of Phases and Texture in Reactively Sputtered Cr_xN_y Thin Films*, Stanford Synchrotron Radiation Laboratory Activity Report, (1998), Proposal 2346MP.

Z. B. Zhao, Z. U. Rek, and J. C. Bilello, *Delamination of CrN Films via X-Ray Topography/Radiography*, Stanford Synchrotron Radiation Laboratory Activity Report, (1998), Proposal 2346MP.

Z. B. Zhao, S. M. Yalisove, Z. U. Rek, and J. C. Bilello, *In-Plane Texture and Stress Anisotropy in Sputtered Cr Films*, Stanford Synchrotron Radiation Laboratory Activity Report, (1998), Proposal 2346MP.

J. F. Whitacre, Z. U. Rek, S. M. Yalisove, and J. C. Bilello, *Phase and Stress State in Ultra Thin Ta Films Via Grazing Incidence X-Ray*

Scattering, Stanford Synchrotron Radiation Laboratory Activity Report, (1997), Proposal 2346MP.

J. F. Whitacre, Z. U. Rek, J. C. Bilello and S. M. Yalisove, *Film Texturing on Rough Surfaces*, Stanford Synchrotron Radiation Laboratory Activity Report, (1997) Proposal 2346MP

J. Hershberger, Z. U. Rek, S. M. Yalisove, J. C. Bilello, *Structure of an Amorphous Thin Buried Layer*, Stanford Synchrotron Radiation Laboratory Activity Report, (1997), Proposal 2346MP.

J. Hershberger, Z. U. Rek, S. M. Yalisove, J. C. Bilello, *Strain Tensors in Amorphous Thin Films*, Stanford Synchrotron Radiation Laboratory Activity Report, (1997), Proposal 2346MP.

Q. Li, J. Liao, J. C. Bilello, Z. U. Rek and D. C. Martin, *WBSXT Study of the DCHD Monomer-Polymer Phase Transition*, Stanford Synchrotron Radiation Laboratory Activity Report, (1997), Proposal 2346MP.

Z. B. Zhao, Z. U. Rek, and J. C. Bilello, *Real Time Observation of Film Cracking and Delamination via High Temperature X-ray Topography*, Stanford Synchrotron Radiation Laboratory Activity Report, (1997), Proposal 2346MP.

Z. B. Zhao, J. Hershberger, A. Chiaramonti, Z. U. Rek and J. C. Bilello, *Synchrotron X-Ray Topographic Studies on Deformation of Single Crystals*, Stanford Synchrotron Radiation Laboratory Activity Report, (1997), Proposal 2346MP

Theses:

Jay F. Whitacre, Doctoral Thesis, 2000
Impurity incorporation, deposition kinetics, and microstructural evolution in sputtered Ta films, Now Senior Scientist JPL, Pasadena, CA

Zhibo B. Zhao, Doctoral Thesis, 1999

Evolution of microstructure and residual stress in sputtered Cr and CrxNy thin films, Now Staff Scientist at Delphi Automotive Group, Shelby Twsp, Michigan.

Jeff G. Hershberger, Doctoral Thesis, 1999
Strain and structure of amorphous boron carbide and silicon carbide thin films, Now Research Scientist Tribology Group, Argonne National Laboratories, Argonne, Illinois.

Beth Ann Rainey, Master of Science, August 2000, Now working at IBM in Burlington, Vermont.

Ankur Agurwal, Master of Science, August, 2000. Now working at AMD, in Sunnyvale, California.

Symposium and other Conference Presentations:

M.J. Daniels, D. King, J.S. Zabinski, Z.U. Rek⁴, and J.C. Bilello, *Microstructure and Chemistry of Annealed AlCuFeCr Quasicrystalline Coatings*, AVS Symp. F - Inter. Conf. On Metall. Coatings and Thin Films - 2002, San Diego, CA, April 2002.

M. J. Daniels, D. King, J. S. Zabinski, and J. C. Bilello, *Stability of Quasicrystalline Phases for As-Deposited AlCuFeCr PVD Coatings*, AVS Symp. B - Inter. Conf. On Metall. Coatings and Thin Films - 2002, San Diego, CA, April 2002.

B. L. French and J. C. Bilello, *In Situ Observations of the Stress Evolution and Delamination Kinetics of Thin Ta Films on Si(100)*, AVS Symp. F - Inter. Conf. On Metall. Coatings and Thin Films - 2002, San Diego, CA, April 2002.

J. C. Bilello, *High-Resolution Synchrotron X-ray Scattering of the Nanostructure of Surface Composite Coatings*, Invited talk at TMS Symposium on 'Surface Composite Coatings', TMS Fall Meeting, October, 2001, Indianapolis, IN.

A.B. Agarwal, B. A. Rainey, S. M. Yalisove, J. C. Bilello, *Nanoindentation and Microstructural Evolution Studies of DC Magnetron Sputtered Chromium Nitride Thin Films*, Spring meeting of the Materials Research Society, April, 2001, San Francisco, CA.

M. J. Daniels, J.C. Bilello, D. Hyland, D. Dew-Hughes, C.R.M. Grovenor, *High Resolution X-ray Characterization of Tl-2212 Superconducting Thin Films*, Spring meeting of the Materials Research Society, April 2001, San Francisco, CA.

S.M. Yalisove and J.C. Bilello, *In-Situ x-ray diffraction during sputter deposition of thin films*, Spring meeting of the Materials Research Society, April 2000. San Francisco, CA.

J.C. Bilello and S.M. Yalisove, *Impurity effects in the initial stages of refractory metal sputter deposition studied via real-time in situ x-ray methods*, Spring meeting of the Materials Research Society, April 2000, San Francisco, CA.

J. F. Whitacre, Z. U. Rek, S M. Yalisove, and J. C. Bilello, *Relating Phase Content to Deposition Kinetics in Ultra-Thin Sputtered Tantalum Films*, Fall 1999 meeting of Amer. Vac. Society.

J. F. Whitacre, Z. U. Rek, J. C. Bilello and S. M. Yalisove, *In-Plane Texture in Evaporated Cr Films*, Fall 1999 meeting of Amer. Vac. Society.

J. F. Whitacre, Z. B. Zhao, B. A. Rainey, S. M. Yalisove, and J. C. Bilello, *Metallic Sputtered Film Evolution Via Real-time/In-situ X-ray Diffraction*, Fall 1999 meeting of Amer. Vac. Society

J. F. Whitacre, Z. U. Rek, J. C. Bilello, and S M. Yalisove, *Testing a Model Used to Describe In-Plane Texturing In Sputtered Mo Films*. Materials Research Society, December 1997 Meeting, Boston MA, Symposium A: Evolution of Surface Morphology and Thin-Film Micro-structure.

J. F. Whitacre, S. M. Yalisove, and J. C. Bilello, *Real-Time In-Situ X-Ray Diffraction Studies of Sputter Deposited Thin Films*, Materials Research Society, December 1997 Meeting, Boston MA, Symposium A: Evolution of Surface Morphology and Thin-Film Microstructure.

Talks at Department of Defense facilities:

John C. Bilello, M. J. Daniels and C. R. M. Grovenor, *Characterization of As-Sputtered and Annealed Quasicrystals* February 1, 2002, DARPA, Institute for Defense Analysis, Arlington, VA.

Personnel:

Faculty and other senior collaborators:

John C. Bilello, Professor, University of Michigan, Principal Investigator

Zofia U. Rek, Senior Research Scientist, Stanford Synchrotron Radiation Laboratory, Menlo Park, CA.

Chris Grovenor, Reader and Deputy Head, Department of Materials, Oxford University, Oxford, United Kingdom.

Post-Doctoral Associates:

None

Graduate Research Assistants:

Benjamin French (started January 2000) passed written Ph. D. qualifying exam February 2000, passed Oral Ph. D. exam December 2001. Needs only to finish Thesis - expected completion date August 2004.

Matthew J. Daniels (started July 1, 1999) passed written Ph. D. qualifying exam September 2000, Passed oral Ph.D. exam March 2001. Needs only to finish Thesis - expected completion date August 2003.

Michelle Tokarz, (started September 2000) passed written Ph. D. qualifying exam February 2001 Passed oral Ph.D. exam November 2002,

Students who worked on this grant and have graduated:

Zhibo Zhao (Ph. D. awarded August 1999) - Staff member, Delphi Automotive Research Laboratory, Shelby Twsp, MI.

Jeff Herschberger (Ph. D. awarded August 1999) - Staff Scientist, Argonne National Laboratory, Argonne, IL.

Jay F. Whitacre (Ph. D. awarded August 2000) - Staff Scientist Jet Propulsion Laboratory, Pasadena, CA.

Beth Ann Rainey (M.S. awarded December 2000) - now at IBM, Burlington, VT.

Ankur Bhushan Agarwal (M. S. awarded December 2000) - now at AMD, Sunnyvale, CA.