

REPORT DOCUMENTATION PAGE

AFRL-SR-AR-TR-03-

0171

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering the data, reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Washington Headquarters Service, Paperwork Project, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Project, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE	3. REPORT TYPE AND DATES COVERED 15Aug 2000 to 14 Aug 2002 FINAL	
4. TITLE AND SUBTITLE IDENTIFICATION AND ELIMINATION OF DEFECTS AND IMPURITIES IN GAN			5. FUNDING NUMBERS 61102F 2305/BX	
6. AUTHOR(S) DR LOOK				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) WRIGHT STATE UNIVERSITY RSCH AND SPONSORED PROGRAMS 3640 COLONEL GLENN HIGHWAY DAYTON OH 45435			8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) AFOSR/NE 4015 WILSON BLVD SUITE 713 ARLINGTON VA 22203			10. SPONSORING/MONITORING AGENCY REPORT NUMBER  F49620-00-1-0347	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION AVAILABILITY STATEMENT APPROVED FOR PUBLIC RELEASE, DISTRIBUTION UNLIMITED			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The Wood-Witt Program is a shorthand title given to a group of coordinated efforts designed to identify and eliminate undesirable defects and impurities in GaN. It was begun by Cohn Wood (ONR) and Jerry Witt (AFOSR) in October of 1999. A few groups were directly funded to work on this task but many others also choose to participate because of the chance to compare results on well characterized samples. Presently, in September of 2002, some 37 people, from 7 different countries, have either supplied material or made measurements, and the total number of participants is at least 79.				
14. SUBJECT TERMS A1GaN/GaN superlattice, terahertz			15. NUMBER OF PAGES	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

20030520 111

**Wright State University:**  
**Semiconductor**  
**Research Center**

134 Oelman Hall  
3640 Col. Glenn Hwy.  
Dayton OH 45435

*Final*  
~~Annual~~ **Technical Report**

to

**Air Force Office of Scientific Research**

Attn: Dr. Gerald L. Witt  
Physics & Electronics Directorate, AFOSR/NE  
4015 Wilson Blvd, Room 713, Arlington, VA 22203  
703-696-8571, Voice  
gerald.witt@afosr.af.mil

**Title: Identification and Elimination of Defects and  
Impurities in GaN**

**Grant F49620-00-1-0347**

**Date of report: 15Sept2001**  
**Period of report: 15August2001 – 14August2002**  
**Period of grant: 15August2000 – 14August2002**

## Introduction

The Wood-Witt Program is a shorthand title given to a group of coordinated efforts designed to identify and eliminate undesirable defects and impurities in GaN. It was begun by Colin Wood (ONR) and Jerry Witt (AFOSR) in October of 1999, and the original goal was to reduce donor  $N_D$  and acceptor  $N_A$  concentrations in state-of-the-art GaN by a factor ten, from the low- $10^{17}$  to the low- $10^{16}$   $\text{cm}^{-3}$  level. A few groups were directly funded to work on this task, but many others also choose to participate because of the chance to compare results on well characterized samples. Presently, in September of 2002, some 37 people, from 7 different countries, have either supplied material or made measurements, and the total number of participants is at least 79, as listed in Appendix I. The first samples investigated were mainly hydride vapor phase epitaxial (HVPE) GaN layers grown on  $\text{Al}_2\text{O}_3$  by Richard Molnar of Lincoln Laboratory/MIT. These layers had thicknesses of up to 70  $\mu\text{m}$ , and world-record 300-K mobilities, at the time, of  $> 950$   $\text{cm}^2/\text{V}\cdot\text{s}$  in the thickest samples. Within a two-year period, this material was thoroughly characterized by many different groups, and quite well understood. For example, it was shown that the donor and acceptor concentrations in the thick samples were  $N_D \cong 1 \times 10^{17}$   $\text{cm}^{-3}$  and  $N_A \cong 3 \times 10^{16}$   $\text{cm}^{-3}$  [1]. However, it was found that the GaN/ $\text{Al}_2\text{O}_3$  interface regions had much higher concentrations, with  $N_D \cong 1 \times 10^{20}$   $\text{cm}^{-3}$  and  $N_A \cong 5 \times 10^{19}$   $\text{cm}^{-3}$  [1-3]. It was further shown that the donors in the bulk region were mostly Si, and in the interface region, O, and that the dominant acceptor was the Ga vacancy ( $V_{\text{Ga}}$ ), everywhere [3]. Measurements on about 100 different HVPE layers, obtained from many independent sources, revealed a highly conductive (degenerate) interface layer in every single case, and the cause was a diffusion of the shallow donor O from the  $\text{Al}_2\text{O}_3$  into the GaN. This O diffusion is concentrated in a region of about 2000  $\text{\AA}$  in the Molnar case, and this same region has a high density of threading dislocations; thus, the O may move into the GaN by pipe diffusion along the dislocations. This phenomenon should be studied further in the next phase of the W-W program, and micro-SIMS measurements should help solve this problem. In any case, the existence of a thin, highly conductive interface layer has a strong effect on electrical and optical properties, and must be considered in the data analysis [2].

In 2001, HVPE GaN material from the Samsung Advanced Institute of Technology (SAIT) became available for the W-W program when AFOSR, in conjunction with their Tokyo arm, AOARD, was able to strike a deal with SAIT. The Samsung GaN wafers had first been grown on  $\text{Al}_2\text{O}_3$ , to a thickness of about 500  $\mu\text{m}$ , then separated from their  $\text{Al}_2\text{O}_3$  substrates, and finally ground, etched and polished to a thickness of

about 200  $\mu\text{m}$  [4]. Since the GaN was separated from the  $\text{Al}_2\text{O}_3$ , experiments could be conducted on both the Ga and N faces. The material was excellent, in fact meeting the original goals of the W-W program. So far, the lowest donor (shallow) and acceptor concentrations measured are:  $N_D = 7 \times 10^{15} \text{ cm}^{-3}$ , and  $N_A = 1.3 \times 10^{15} \text{ cm}^{-3}$  [5]. The highest 300-K mobility is  $1320 \text{ cm}^2/\text{V}\cdot\text{s}$ , and the highest peak mobility is close to  $12000 \text{ cm}^2/\text{V}\cdot\text{s}$ . Donor-bound exciton photoluminescence (PL) linewidths are less than  $0.5 \text{ meV}$  [6], and both O and Si donors have been identified by PL. In contrast to the Molnar GaN, the dominant donor in the bulk seems to be O, not Si, but the dominant acceptor is still the Ga vacancy. Partly because of the low free-carrier concentrations, Schottky barriers are excellent, having barrier heights of  $1.27 \text{ eV}$  on the Ga face, and  $0.75 \text{ eV}$  on the N face [7]. Furthermore, the Samsung GaN is very useful for electron-irradiation experiments, because of the small background concentrations of donors, acceptors and traps. It also has a small threading dislocation density,  $< 1 \times 10^6 \text{ cm}^{-2}$ , at the top (Ga) face. This means that the average distance between dislocations is about  $10 \mu\text{m}$ , so that it should be possible to study the Cottrell atmosphere of impurities and defects surrounding each dislocation. The micro-SIMS capability at Ohio State University (Prof. Brillson) should be very useful in this investigation. Overall, many experiments have been performed on the relatively small amount of material received from Samsung, and 35% of the publications listed in Appendix II are related to these studies. It is likely that Samsung GaN wafers will have a significant impact on the quest to develop a GaN substrate for homoepitaxy, and it is noteworthy that the most detailed characterization studies on these wafers have come out of the W-W program.

### Electron irradiation for defect studies

To create point defects, in our laboratory, we use high-energy (0.7-2.0 MeV) electrons from a van de Graaff accelerator. Also, lower energy electrons (0.3 – 1.0 MeV) are available from a similar but smaller machine at Hanscom AFB. Most of the energy loss in high-energy electron bombardment occurs from electron-electron, rather than electron-nucleus, collisions. Such e-e collisions limit the electron range in GaN to about  $0.7 \text{ mm}$  for 1-MeV electrons, for example. For epitaxial layers, of thickness  $100 \mu\text{m}$  or less, the electrons lose very little energy in traversing the sample. If a relativistic electron of energy  $E$  makes a *direct* hit on a nucleus, it will transfer a maximum energy  $E_m$  given by

$$E_m = \frac{2E(E + 2m_e c^2)}{Mc^2} = \frac{2.147 \times 10^{-9} E(E + 1.022 \times 10^6)}{A} \quad (1)$$

where  $m_e$  and  $M$  are the electron and ion masses, respectively,  $A$  is the atomic weight, and the energies are in eV. The threshold energy  $E_{th}$  necessary to produce an atomic displacement is then just given by the condition  $E_m = E_d$ , where  $E_d$  is the displacement energy. In GaN, Van Vechten [8] has estimated  $E_d$  values of 32.5 and 24.3 for N and Ga displacements, respectively, and it can be shown from Eq. 1 that these values lead to threshold energies  $E = 0.18$  and  $0.51$  MeV, for production of  $V_N-N_i$  and  $V_{Ga}-Ga_i$  Frenkel pairs, respectively.

### Temperature-dependent Hall-effect (T-Hall)

T-Hall measurements constitute the standard method of determining donor  $N_D$  and acceptor  $N_A$  concentrations in semiconductor materials [9]. Ideally, the temperature dependences of both the Hall mobility  $\mu_H$  and the carrier concentration  $n$  (assumed n-type) are fitted to determine  $N_D$ ,  $N_A$ , and  $E_D$ , the donor activation energy. The mobility, for elastic scattering processes, can be calculated from  $\mu_H = e\langle\tau^2\rangle/m^*\langle\tau\rangle$ , where  $\langle\tau^n\rangle$  denotes an average of the  $n$ th power of the relaxation time  $\tau(E)$  over electron energy  $E$ . The relaxation rate  $\tau^{-1}(E)$  has contributions from various scattering mechanisms:

$$\tau^{-1}(E) = \tau_{ac}^{-1}(E) + \tau_{pe}^{-1}(E) + \tau_{po}^{-1}(E) + \tau_{ii}^{-1}(E) + \tau_{dis}^{-1}(E) \quad (2)$$

in which acoustical-mode lattice vibrations scatter electrons through the deformation potential ( $\tau_{ac}$ ) and piezoelectric potential ( $\tau_{pe}$ ); optical-mode vibrations through the polar potential ( $\tau_{po}$ ); ionized impurities and defects through the screened coulomb potential ( $\tau_{ii}$ ); and charged dislocations, also through the coulomb potential ( $\tau_{dis}$ ). The strengths of these various scattering mechanisms depend upon certain lattice parameters, such as dielectric constants and deformation potentials, and extrinsic factors, such as donor, acceptor, and dislocation concentrations,  $N_D$ ,  $N_A$ , and  $N_{dis}$ , respectively. For thick, HVPE GaN layers,  $N_{dis}$  is usually not important, and the only fitting parameter is  $N_A$ , since the ionized defect/impurity density is given by  $N_i = 2N_A + n \approx 2N_A + n_H$ , where  $n_H$  is measured in the experiment. In reality, since polar-optical scattering is not elastic, we often use a more accurate fitting scheme for  $\mu_H$  vs.  $T$  [9].

To determine  $N_D$  and  $E_D$  we must solve the charge-balance equation (CBE):

$$n + N_A = \frac{N_D}{1 + n / \phi_D} \quad (3)$$

where  $\phi_D = (g_0/g_1)N_C' \exp(\alpha_D/k)T^{3/2} \exp(-E_{D0}/kT)$ . Here,  $g_0/g_1$  is a degeneracy factor ( $= 1/2$  for an s-state),  $N_C'$

$= 2(2\pi m_n^* k)^{3/2} / h^3$ , where  $h$  is Planck's constant,  $E_D$  is the donor energy,  $k$  is Boltzmann's constant, and  $E_{D0}$  and  $\alpha_D$  are defined by  $E_D = E_{D0} - \alpha_D T$ . If more than one donor exists within a few  $kT$  of the Fermi energy, then equivalent terms, involving  $N_{D2}$ ,  $N_{D3}$ , etc., are added on the right-hand side of Eq. 3.

Recently we have applied the above analyses to  $\mu_H$  vs.  $T$  (Fig. 1) and  $n_H$  vs.  $T$  (Fig. 2) data for a very pure free-standing HVPE GaN layer grown by Samsung [10]. The 300-K and peak mobilities of this sample were 1245 and 7400  $\text{cm}^2/\text{V-s}$ , respectively, and the fitted donor and acceptor concentrations were  $6.7 \times 10^{15}$  and  $1.7 \times 10^{15} \text{ cm}^{-3}$ , respectively. Interestingly, this value of  $N_A$  is very close to the  $V_{\text{Ga}}$  concentration measured by PAS in similar material [11]. In fact,  $V_{\text{Ga}}$  is often the dominant acceptor in undoped HVPE GaN, over a wide range of acceptor concentrations [3]. After 1-MeV electron irradiation, both  $N_D$  and  $N_A$  increase, each by about  $1 \text{ cm}^{-3}$  for each bombarding electron per  $\text{cm}^2$ , giving a production rate of about  $1 \text{ cm}^{-1}$  [1]. From various considerations, it has been argued that the donor is likely an N vacancy  $V_N$ , and the acceptor an N interstitial  $N_i$  [1]. Also determined from the experiment is the donor activation energy  $E_D \approx 0.06 \text{ eV}$ . This value is compatible with the theoretical conclusion that  $V_N$  should be a shallow donor [12]. Also, theory predicts  $N_i$  to have a deep-acceptor state [12], consistent with the Hall data. If we are indeed seeing only N-sublattice damage, then the absence of Ga-sublattice damage is a mystery.

### Deep level transient spectroscopy (DLTS)

DLTS is a technique capable of determining electron and hole trap parameters: concentration, activation energy, and capture cross section [9]. In its common form, a reverse-biased Schottky barrier or p-n junction is subjected to a forward-bias pulse in order to flood the depletion region with electrons (or holes), and thus temporarily fill the traps in that region. Upon returning to the original reverse bias, the temporarily trapped electrons or holes will be re-emitted, as illustrated in Fig. 3. For experiments involving a Schottky barrier on n-type material, there will be a capacitance  $C$  immediately before the pulse, and  $C - \Delta C$  immediately afterwards. In first order, the trap concentration  $N_T$  is given by  $N_T = -2N_D(\Delta C/C)$ , where  $N_D$  is the net shallow donor concentration. As time proceeds after the filling pulse, the capacitance will return to its original value  $C$ , usually in an exponential manner. In the box-car technique, this exponential is sampled at two times,  $t_1$  and  $t_2$ , to effect a "rate window" defined by  $r = \ln(t_2/t_1)/(t_2 - t_1)$ . As temperature is swept upwards, the emission rate  $e_n$  of a particular trap increases, according to  $e_n = CT^2 \exp(-E/kT)$ , where  $C$  is a constant involving the capture cross section, and  $E$  is an activation energy, consisting of the trap energy  $E_T$

plus the cross-section barrier height  $E_{\sigma}$ , if non-zero (i.e.,  $E = E_T + E_{\sigma}$ ). As illustrated in Fig. 4, the DLTS "spectrum" then consists of a series of peaks due to different traps  $N_{Ti}$ , with each peak occurring at the temperature for which  $e_{ni} = r$ .

Fig. 1. Mobility fit for Samsung freestanding GaN layer.


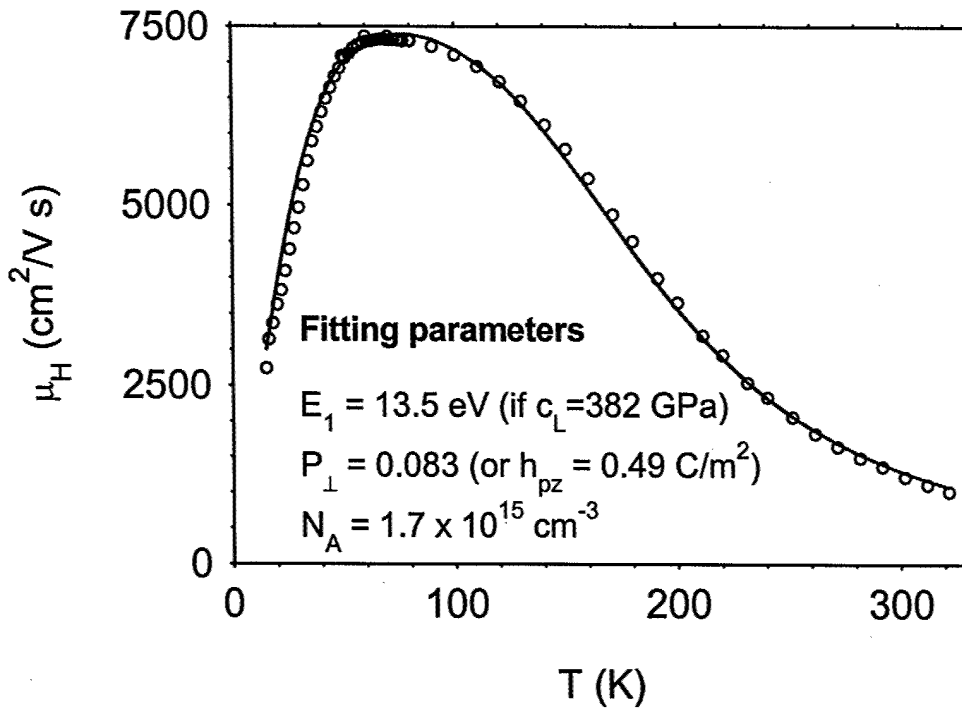


Fig. 2. Carrier concentration fit for Samsung freestanding GaN layer:  $n_H$  is the Hall concentration and  $n$  is the true concentration.

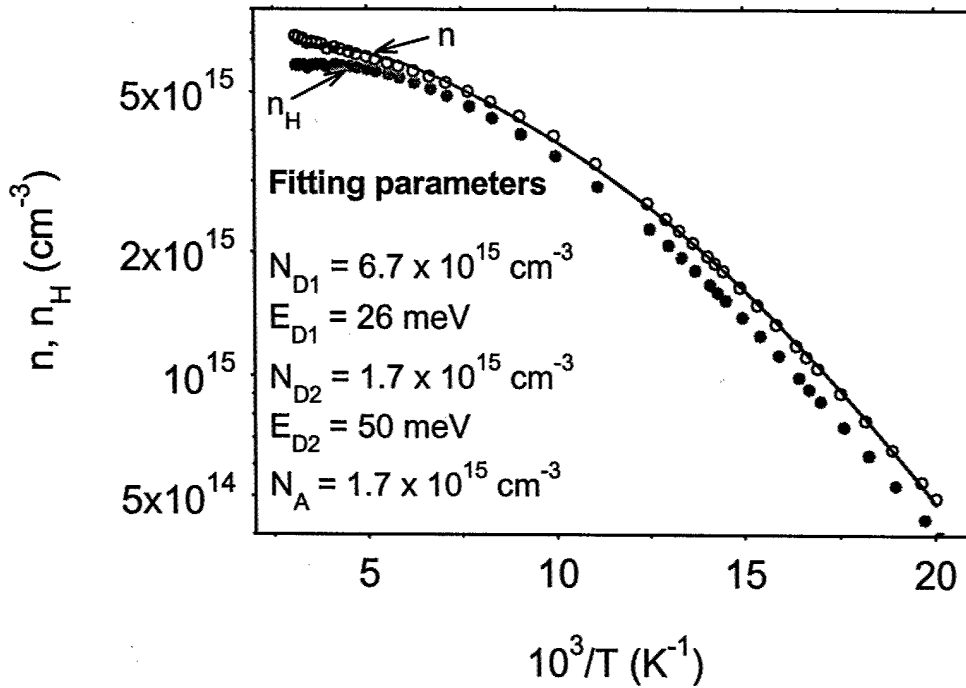

Actually, the simple formula,  $N_T = -2N_D(\Delta C/C)$ , holds only if  $N_T/N_D \ll 1$ , and if  $E_T$  is not very large. We expect these conditions to be often violated in AlGaIn. Fortunately, we have derived a general formula, contained in a recent article on DLTS [13] written for the *Encyclopedia of Materials: Science and Technology*. It can be shown that a precise form of  $\Delta C/C$  is

$$\frac{\Delta C}{C} = \frac{\left[ 1 + f_\lambda \frac{N_T(w_r - \lambda)}{N_D^{net}(w_r)} \right]^{1/2} - 1}{\left[ 1 + f_\lambda \frac{N_T(w_r - \lambda)}{N_D^{net}(w_r)} \right]^{1/2}} \quad (4)$$

where

$$w_r = \sqrt{\frac{2\varepsilon(\phi_B - V_r - E_{C\infty}/e - kT/e)}{eN_D^{net}}} \quad (5)$$

and

$$\lambda = \left( \frac{2\varepsilon(E_T - E_{C\infty} - kT)}{e^2 N_D^{net}} \right)^{1/2} \quad (6)$$

The positions of  $w_r$  and  $\lambda$  are shown in Fig. 3. The most important part of Eq. 4 is a unique expression for  $f_\lambda$  that is valid for both high trap concentrations and deep trap energies [14]:

$$f_\lambda = \frac{1}{\left[ 1 + \frac{\alpha\beta^{1/2}}{(1+\alpha-\alpha\beta)^{1/2}} \right]^2} \left\{ F(\alpha, \beta) - 2 \frac{\beta^{1/2}}{(1+\alpha-\alpha\beta)^{1/2}} \left[ 1 - (1 - F(\alpha, \beta))^{1/2} \right] \right\} \quad (7)$$

where

$$F(\alpha, \beta) = \frac{1+\alpha}{1+\alpha-\alpha\beta} \frac{V_f - V_r}{\phi_B - E_{C\infty} - V_r - kT/e} \quad (8)$$

The various symbols are as follows:  $\varepsilon$  is the static dielectric constant;  $\phi_B$  is the Schottky barrier height;  $V_f$  and  $V_r$  are the forward and reverse bias voltages, respectively;  $E_{C\infty}$  is the flat conduction band energy, far from the surface;  $N_D^{net} = N_D - N_A$ ;  $\alpha = N_T/N_D$ ; and  $\beta = (E_T - E_{C\infty} - kT)/e(\phi_B - E_{C\infty}/e - V_r - kT/e)$ . Note that Eq. 4 explicitly contains  $N_D^{net}$  evaluated at  $w_r$ , and  $N_T$  at  $(w_r - \lambda)$ , a fact that can be important if the layer is inhomogeneous or if a profile of  $N_T$  is being generated.

Fig. 3. Effect of a metal Schottky barrier (energy  $e\phi_B$ ) on the surface of GaN. Filled circles denote states occupied by electrons, and empty circles, unoccupied. As demonstrated by the arrows, filled states above the Fermi level  $E_F$  (set at  $E = 0$ ) will emit their electrons to the conduction band and this phenomenon results in a capacitance transient. The various symbols are defined in the text.


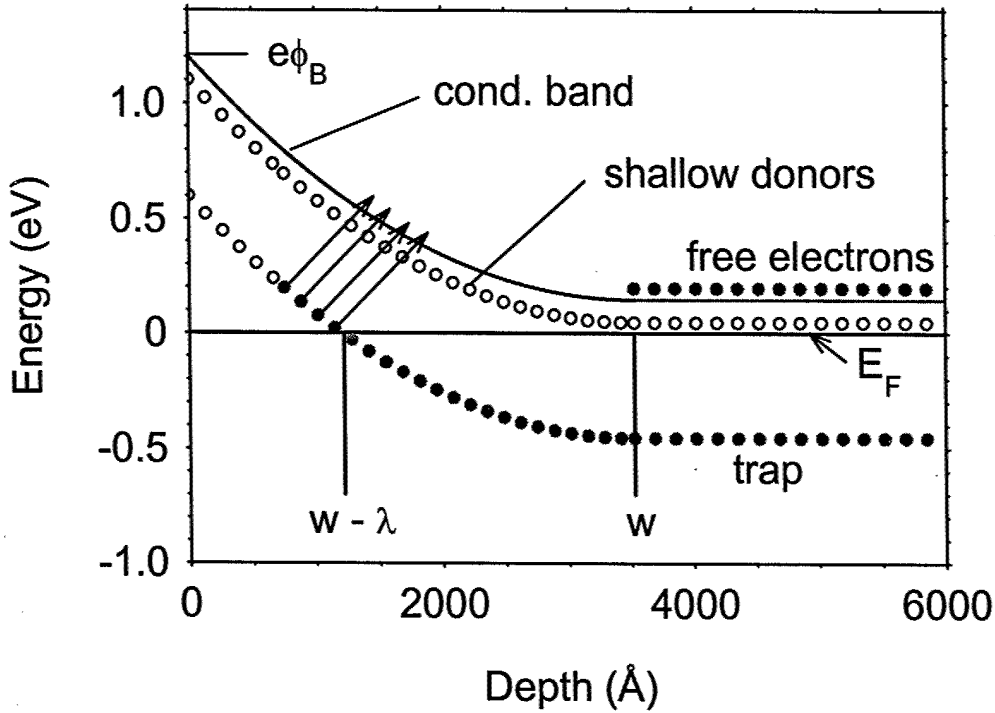


Fig. 4. Plots of  $-\Delta C/C$  for a freestanding GaN sample as a function of emission rate  $e_n$ . Five traps are identified:  $A_1$ , A, B, C, and D. The conditions are:  $V_r = -5.0$  V,  $V_f = 0$  V, and  $t_p = 1$  ms.

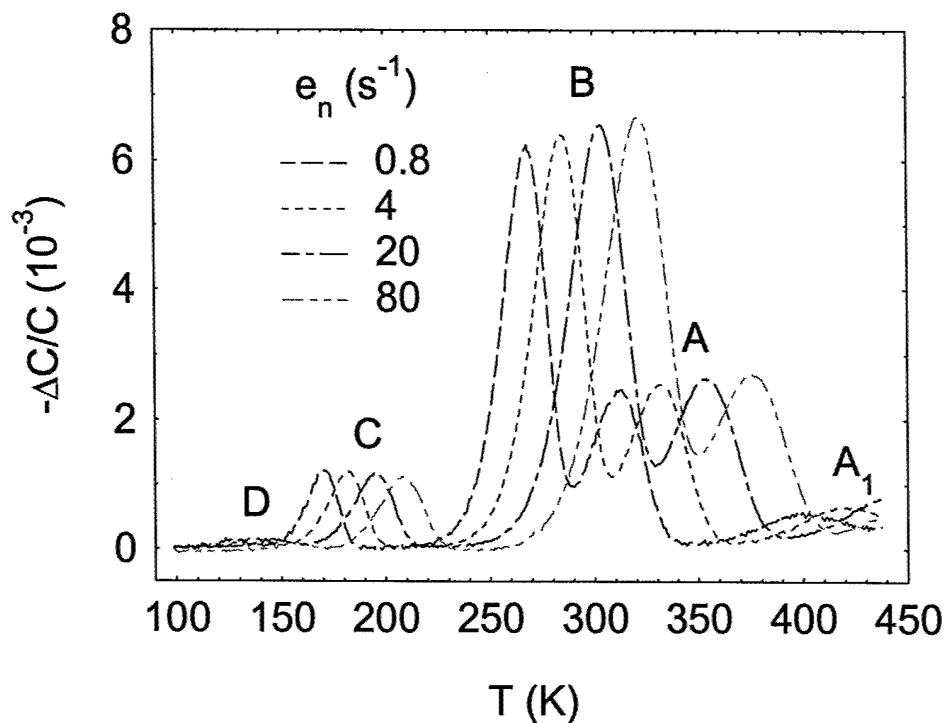

In GaN, two common defect-related traps, designated here as ED and AD, are nearly always observed, no matter what type of irradiation is used. For the rate window set at  $r = 4$  s<sup>-1</sup>, traps ED and AD have DLTS signal peaks at about 100 and 400 K, respectively. Other traps have also been seen, as outlined in Table 1, but virtually all workers have at least seen ED and AD. Trap ED was first reported by Fang et al. [15] to have an energy  $E$  of 0.18 eV, but later analysis by Polenta et al. [16] revealed that it consisted of two overlapping traps, each with a thermal energy component  $E_T$  of 0.06 eV, and capture-cross-section components  $E_\sigma$  of 0 and 0.05 eV, respectively. Indeed, Goodman et al. [17] have recently found that ED consists of three components, but their source of electrons (0.25 – 2.5 MeV, <sup>90</sup>Sr) was different from that used by Fang, Polenta, et al. (1-MeV, van de Graaff). The combined production rate of all of the components is about 1 cm<sup>-1</sup> [17], the same as that determined from the T-Hall analysis [1], and since the thermal energies are also the same (0.06 eV), it is almost certain that a common defect (probably  $V_N$ ) is being observed. The


different DLTS trap components could perhaps correspond to different separations of the Frenkel-pair components,  $V_N$  and  $N_I$  [18]. The existence of several components in ED also can explain the slight differences in overall peak position, 0.13 – 0.20 eV, seen by various workers.

It is important to emphasize that the various components of trap ED appear not only in irradiated samples, but also in as-grown, ion-implanted, and contact-metal-deposited samples. In MBE layers [19,20,21], the concentration of trap  $E_1$ , one of the components of  $E_D$ , increases with decrease of N flux during growth, again supporting its identification with  $V_N$ . A strong increase of the trap  $E_1$  DLTS signal with pulse length is illustrated in Fig. 5. This shows that it has a small capture cross section, perhaps due to a repulsive barrier. Incidentally, trap D also must have a defect nature, because we have recently shown that it can be created with plasma etching.

### **Positron annihilation spectroscopy (PAS)**

Positrons injected into defect-free GaN are annihilated by the core atomic electrons in a mean time of 160 – 165 ps. However, if there are negatively charged vacancies present, some of the positrons will become trapped at those locations, and will have longer lifetimes, because of the reduced electron density at vacancies. In the case of GaN, Ga vacancies (but not N vacancies) would be expected to fill this role, and indeed, PAS has been used to identify and quantify  $V_{Ga}$ -related defects [22]. For example, it has been shown that 2-MeV electrons produce  $V_{Ga}$  centers at a rate of about  $1 \text{ cm}^{-1}$  in bulk, semi-insulating GaN [11]. Moreover, comparisons of  $V_{Ga}$  concentrations with acceptor concentrations  $N_A$  in a series of undoped, n-type HVPE GaN samples, with  $N_A$  ranging from  $10^{15}$  to  $10^{19} \text{ cm}^{-3}$ , show that  $[V_{Ga}] \approx N_A$ , to within experimental error [3,11]. Thus, it appears that  $V_{Ga}$ , and not any impurity, is the dominant acceptor in HVPE GaN, and probably in other types of undoped GaN, also. Indeed, theory predicts that  $V_{Ga}$  centers should be abundant in n-type GaN[23].

Fig. 5. DLTS signal  $-2N_D(\Delta C/C)$  for a MBE GaN layer. Note the strong dependence of trap  $E_1$  on forward-bias pulse length  $t_p$ . The conditions are:  $e_n = 10 \text{ s}^{-1}$ ,  $V_r = -3.0 \text{ V}$ , and  $V_f = 0.5 \text{ V}$ .

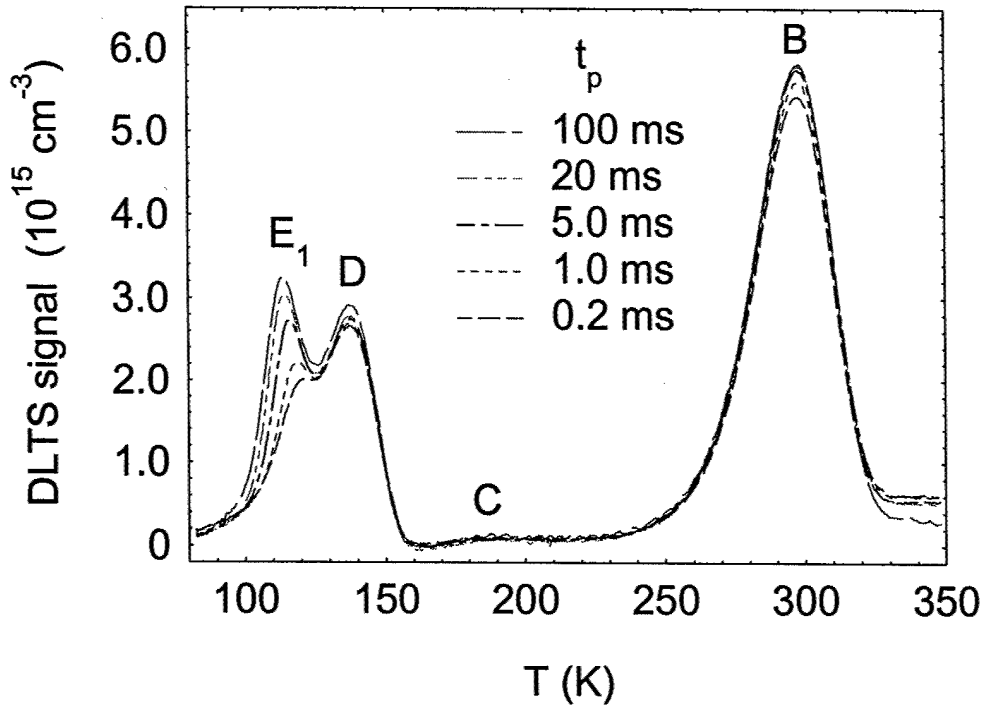

### Photoluminescence (PL)

Two, infrared PL bands, at roughly 0.85 and 0.93 eV, are produced by 2.5-MeV electrons [24-27]. Both bands are broad, but the former has a sharp zero-phonon line (ZPL) at 0.88 eV and accompanying phonon structure. Some workers have proposed that the lower-energy band with the ZPL is much like the well-known  $O_p$  band in GaP, and, in the GaN case, involves a transition between a deep ground state of  $O_N$  (at  $E_C - 0.90 \text{ eV}$ ) and an excited state of  $O_N$  (at  $E_C - 0.02 \text{ eV}$ ), along with associated phonon side bands [27]. However, there are several apparent problems with this model, and another defect, an  $O_N\text{-Ga}_I$  complex, may be a better candidate [28].

### Dislocation Studies

Recently, threading-edge dislocations (TEDs) have been shown to be negatively charged in n-type GaN, behaving as a line charge with a linear charge density of about  $1e$  per c-lattice distance,  $5.185 \text{ \AA}$  [29]. Thus, these dislocations are acceptor-like, and theoretical studies are consistent with this picture, suggesting that the dislocation cores in n-type GaN may contain Ga vacancies [30,31], or  $V_{\text{Ga}}\text{-O}_n$  complexes, with  $n = 1 - 3$  [32]. It might be assumed that simple  $V_{\text{Ga}}$  centers along the core would have a charge of  $-3$  each, but it turns out that electron-electron repulsion reduces the charge to about  $-1$  each, for typical material with  $n \sim 1 \times 10^{17} \text{ cm}^{-3}$  [31]. For HVPE GaN on  $\text{Al}_2\text{O}_3$ , the interface region has a very high TED density,  $N_{\text{dis}} \sim 10^{10} - 10^{11} \text{ cm}^{-2}$ , and an even higher misfit dislocation density,  $N_{\text{mis}} > 10^{12} \text{ cm}^{-2}$ , as deduced by transmission electron microscopy (TEM) measurements [3]. Also, from secondary-ion mass spectroscopy (SIMS) measurements,  $[\text{O}] > 10^{19} \text{ cm}^{-3}$  in this region; from PAS,  $[V_{\text{Ga}}] > 10^{19} \text{ cm}^{-3}$ ; and from Hall-effect and electrochemical C-V (ECV) measurements,  $n > 10^{19} \text{ cm}^{-3}$  [3]. The picture that emerges here is that the donors are O, and the acceptors are  $V_{\text{Ga}}$ , but the  $V_{\text{Ga}}$  in this case are probably associated with the dislocations, either as isolated centers along the core, or as  $V_{\text{Ga}}\text{-O}$  complexes. Interestingly, O is the dominant donor only in the interface region, since SIMS and T-Hall data show that Si takes over in the bulk region. However, PAS and T-Hall measurements show that  $V_{\text{Ga}}$  is the dominant acceptor everywhere, both in the interface and bulk regions [3].

## References

- [1] D.C. Look et al, Phys. Rev. Lett. **79**, 2273 (1997).
- [2] D.C. Look and R.J. Molnar, Appl. Phys. Lett. **70**, 3377 (1997).
- [3] D.C. Look et al, Solid State Commun. **117**, 571 (2001).
- [4] E. Oh et al, Appl. Phys. Lett. **78**, 273 (2001).
- [5] D.C. Look et al, unpublished.
- [6] D.C. Reynolds et al, Appl. Phys. Lett. **77**, 2879 (2000).
- [7] Z-Q. Fang et al, Appl. Phys. Lett. **78**, 2178 (2001).
- [8] J.A. Van Vechten, *Handbook on Semiconductors*, vol. 3, (North Holland, Amsterdam, 1980) ch. 1.
- [9] D.C. Look, *Electrical Characterization of GaAs Materials and Devices* (Wiley, New York 1989).
- [10] D.C. Look and J.R. Sizelove, Appl. Phys. Lett. **79**, 1133 (2001).
- [11] K. Saarinen, private communication.
- [12] P. Boguslawski et al, Phys. Rev. B **51**, 17255 (1995).
- [13] D.C. Look and Z-Q. Fang, "Deep Level Transient Spectroscopy", in *The Encyclopedia of Materials: Science and Technology*, ed. by S. Mahajan (Elsevier, Oxford) in press.
- [14] D.C. Look and J.R. Sizelove, J. Appl. Phys. **78**, 2848 (1995).
- [15] Z-Q. Fang et al, Appl. Phys. Lett. **72**, 448 (1998).
- [16] L. Polenta et al, Appl. Phys. Lett. **76**, 2086 (2000).
- [17] S.A. Goodman et al, Appl. Phys. Lett. **78**, 3815 (2001).
- [18] D.C. Look et al, Phys. Rev. Lett. **82**, 2552 (1999).
- [19] Z-Q. Fang et al, in: Proc. 2000 Int. Semiconducting and Insulating Mater. Conf., IEEE, Piscataway, 2000 (p. 35).
- [20] Z-Q. Fang et al, Appl. Phys. Lett. **72**, 2277 (1998).
- [21] D.C. Look et al, MRS Internet J. Nitride Semicond. Res. **5S1**, W10.5 (2000).
- [22] K. Saarinen et al, Appl. Phys. Lett. **75**, 2441 (1999).
- [23] C. Stampfl and C.G. Van de Walle, Phys. Rev. B **65**, 155212 (2002).
- [24] M. Linde et al, Phys. Rev. B **55**, R10177 (1997).
- [25] I.A. Buyanova et al, Appl. Phys. Lett. **73**, 2968 (1998).
- [26] W.M. Chen et al, Phys. Rev. B **58**, R13351 (1998).

- [27] K.H. Chow et al, Phys. Rev. Lett. **85**, 2761 (2000).
- [28] C.J. Fall et al, Mater. Sci. and Eng. B **82**, 88 (2001).
- [29] D.C. Look and J.R. Sizelove, Phys. Rev. Lett. **82**, 1237 (1999).
- [30] A.F. Wright and U. Grossner, Appl. Phys. Lett. **73**, 2751 (1998).
- [31] K. Leung et al, Appl. Phys. Lett. **74**, 2495 (1999).
- [32] J. Elsner et al, Phys. Rev. B **58**, 12571 (1998).

## Appendix I. Participants in Wood-Witt Program (as of Sept, 2002)

Name	Institution	E-mail address	Specialty
F. Danie Auret	University of Pretoria, South Africa	fauret@postino.up.ac.za	DLTS
Michael Alexander	AFRL, Hanscom AFB, MA	michael.alexander@hanscom.af.mil	Growth, Char.
David Bliss	AFRL/SNHX, Hanscom AFB, MA	bliss@plh.af.mil	Growth
Lionel Bouthillette	AFRL/SNHC, Hanscom AFB, MA	lionel.bouthillette@hanscom.af.mil	PL
Len Brillson	Ohio State University	brillson.1@osu.edu	Micro-CL
Jeff Brown	AFRL/MLPS, WPAFB, OH	jeff.brown@wpafb.af.mil	AFM
Mike Callahan	AFRL/SNHX, Hanscom AFB, MA	michael.callahan@hanscom.af.mil	Growth
Bill Carlos	Naval Research Laboratory	carlos@bloch.nrl.navy.mil	EPR
Anna Cavallini	University of Bologna, Italy	anna.cavallini@bo.infn.it	PC, DLTS, EBIC
Leonid Chernyak	University of Central Florida	chernyak@physics.ucf.edu	EBIC
Vladimir Dmitriev	TDI, Inc.	vladimir@tdii.com	Growth
Russell Dupuis	University of Texas	dupuis@mail.utexas.edu	Growth, Char.
Zhaoqiang Fang	Wright State University	zhaoqiang.fang@wright.edu	DLTS
Gary Farlow	Wright State University	gary.farlow@wright.edu	Irradiation
Randy Feenstra	Carnegie-Mellon University	feenstra+@andrew.cmu.edu	Growth, Char.
Doru Florescu	Brooklyn College of CUNY	dfloresc@its.brooklyn.cuny.edu	Ther. Cond.
Jaime Freitas	Naval Research Laboratory	jaime.freitas@nrl.navy.mil	PL
Evan Glaser	Naval Research Laboratory	glaser@bloch.nrl.navy.mil	ODMR
Robert Grober	Yale	robert.grober@yale.edu	PL (profiling)
Shiping Guo	EMCORE Corp.	shipping_guo@emcore.com	Growth (?)
Karl Harris	Electro-optics Center, Pittsburgh	kharris@psu.edu	PL mapping
Ben Heying	UC Santa Barbara	benh@mrl.ucsb.edu	Growth
John Hoelscher	Wright State University	john.hoelscher@wpafb.af.mil	Hall
Julia Hsu	Lucent Technologies	jhsu@physics.lucent.com	SCM, etc.
Thomas Jenkins	AFRL/SNDM, WPAFB, OH	thomas.jenkins@wpafb.af.mil	Noise
Dan Johnstone	AFOSR	dan.johnstone@afosr.af.mil	Prog. Mgt.
Rex Jones	AFRL/MLPS, WPAFB, OH	rex.jones@wpafb.af.mil	PL
Thomas Kazior	Raytheon Commercial Electronics	tkazior@rffc.raytheon.com	Devices
Chae-Deok Lee	Carnegie-Mellon University	cdlee@andrew.cmu.edu	Growth (?)
Z. Liliental-Weber	Lawrence Berkeley National Lab.	z_liliental-weber@lbl.gov	TEM
Sukit Limpijumnong	Xerox PARC	slim@parc.xerox.com	Theory
Cole Litton	AFRL/MLPA, WPAFB, OH	cole.litton@wpafb.af.mil	Prog. Mgt.
David Look	Wright State University	david.look@wpafb.af.mil	Hall
Edgar Martinez	DARPA	emartinez@darpa.mil	Prog. Mgt.
J.W. McCamy	Coming Inc.	mccamyjw@coming.com	XRD, EBIC (?)
Floyd McDaniel	University of North Texas	fdmcdan@sandia.gov	SIMS

Bill Mitchel	AFRL/MLPS, WPAFB, OH	william.mitchel@wpafb.af.mil	Hall
Rich Molnar	MIT Lincoln Laboratory	rmolnar@ll.mit.edu	Growth
Hadis Morkoc	Virginia Commonwealth Univ.	hmorkoc@vcu.edu	Growth,Char.
Tom Myers	West Virginia University	tmyers@wvu.edu	Growth,PC
Ken Nakano	AFRL/SNDD, WPAFB, OH	kenichi.nakano@wpafb.af.mil	Devices
John Northrup	Xerox PARC	northrup@parc.xerox.com	Theory
Steve Novak	Evans East, Inc.	snovak@evanseast.com	SIMS
Andrei Osinsky	Coming Inc.	ossinskiav@coming.com	XRD,EBIC
Jon Pelz	Ohio State University	pelz.2@osu.edu	BEEM
Eddie Piner	Nitronex	edwin_piner@nitronex.com	Growth
Laura Polenta	University of Bologna, Italy	laura.polenta@bo.infm.it	DLTS
Fred Pollak	Brooklyn College of CUNY	fhpbcc@cunyvm.cuny.edu	Ther.Cond.
AlexanderPolyakov	Inst. Of Rare Metals, Moscow	polyakov@gimet.ru	Optical DLTS
Fernando Ponce	Arizona State University	ponce@asu.edu	Micro-CL
MichaelReshchikov	Virginia Commonwealth Univ.	mreshchi@saturn.vcu.edu	PL
Steve Ringel	Ohio State University	ringel@ee.eng.ohio-state.edu	DLTS
Lawrence Robins	NIST	lawrence.robins@nist.gov	Micro-xray, etc.
Kimmo Saarinen	Helsinki Univ. of Tech., Finland	ksa@fyslab.hut.fi	Pos. Annih.
Norman Sanford	NIST	sanford@boulder.nist.gov	Micro-xray, etc.
Brian Skromme	Arizona State University	skromme@asu.edu	PL
Kurt Smith	Raytheon Commercial Electronics	kurt_v_smith@rfc.raytheon.com	Devices
Jim Speck	UC Santa Barbara	speck@mrl.ucsb.edu	Growth,TEM
Ed Stutz	AFRL/MLPS, WPAFB, OH	charles.stutz@wpafb.af.mil	ECV
Xiaoling Sun	Ohio State University	sun.131@osu.edu	CL
Changmo Sung	Univ. of Massachusetts, Lowell	changmo_sung@uml.edu	TEM, AFM
Mahendra Sunkara	University of Louisville	mahendra@louisville.edu	Growth
Vladimir Tassev	AFRL/SNHC, Hanscom AFB, MA	vladimir.tassev@hanscom.af.mil	Growth (?)
Mike Tinston	CSCI	mtinston@csci-va.com	webpage
Abbas Torabi	Raytheon RFC	abbas_torabi@raytheon.com	XRD
Pat Treado	ChemIcon	treado@chemimage.com	PL,Raman map
Chris Van de Walle	Xerox-PARC	vandewalle@parc.xerox.com	Theory
G. David Via	AFRL/SND, WPAFB, OH	glen.via@wpafb.af.mil	FBIC (?)
Eicke Weber	UC Berkeley	weber@socrates.berkeley.edu	EPR
Bruce Wessels	Northwestern University	b-wessels@northwestern.edu	Growth,Char.
David Weyburne	AFRL/SNHX, Hanscom AFB, MA	weyburned@plh.af.mil	Growth
Jan Weyher	High Pressure Res. Ctr., Warsaw	weyher@unipress.waw.pl	TEM,Etching
Gerald Witt	AFOsr	gerald.witt@afosr.af.mil	Prog. Mgt.
Colin Wood	ONR	woodc@onr.navy.mil	Prog. Mgt.
Emily Qing Yang	UC Berkeley	qingyang@uclink4.berkeley.edu	TRPL
Jinwei Yang	University of South Carolina	yangj@enr.sc.edu	Growth

Ed Yu	UC San Diego	ety@ece.ucsd.edu	SCM, etc.
Phil Yu	Kwangju Inst. Sci. & Tech., Korea	pwyu@kjist.ac.kr	T-dep PL
John Zolper	ONR	zolperj@onr.navy.mil	Prog. Mgt.
Mary Ellen Zvanut	Univ. of Alabama, Birmingham	mezvanut@uab.edu	EPR

**Appendix II. Wood-Witt related publications (since August 2000) involving WSU personnel.**

1. Z-Q. Fang, L. Polenta, J.W. Hemsky, and D.C. Look, "Deep Centers in As-Grown and Electron-Irradiated n-GaN", in *2000 International Semiconducting and Insulating Materials Conference*, ed. By C. Jagadish and N.J. Welham (IEEE, Piscataway, NJ, 2000) p. 35. Mar01
2. D.C. Reynolds, D.C. Look, B. Jogai, J.E. Hoelscher, R.E. Sherriff, and R.J. Molnar, "Strain Variation with Sample Thickness in GaN Grown by Hydride Vapor Phase Epitaxy", *J. Appl. Phys.* **88**, 1460 (2000). Aug00
3. S.H. Goss, A.P. Young, L.J. Brillson, D.C. Look, and R.J. Molnar, "Direct Observation of Bulk and Interface States in GaN on Sapphire Grown by Hydride Vapor Phase Epitaxy" *Mater. Res. Soc. Symp. Proc.* **639**, G3.59.1 (2001). Oct01
4. D.C. Look, C.E. Stutz, R.J. Molnar, K. Saarinen, and Z. Liliental-Weber, "Dislocation-Independent Mobility in Lattice-Mismatched Epitaxy: Application to GaN", *Solid State Commun.* **117**, 571 (2001). Feb01
5. L. Chernyak, A. Osinsky, G. Nootz, A. Schulte, J. Jasinski, M. Benamara, Z. Liliental-Weber, D.C. Look, and R.J. Molnar, "Electron Beam and Optical Depth Profiling of Quasi-Bulk HVPE GaN", *Appl. Phys. Lett.* **77**, 2695 (2000). Oct00
6. J.W.P. Hsu, D.V. Lang, S. Richter, R.N. Kleiman, A.M. Sergent, D.C. Look, and R.J. Molnar, "Impurity Band in the Interfacial Region of GaN Films Grown by HVPE", *J. Electronic Mater.* **30**, 115 (2001). Mar01
7. D.C. Reynolds, D.C. Look, B. Jogai, A.W. Saxler, S.S. Park, and J.W. Hahn, "Identification of the  $\Gamma_5$  and  $\Gamma_6$  Free Excitons in GaN", *Appl. Phys. Lett.* **77**, 2879 (2000). Oct00
8. Z.-Q. Fang, D. C. Look, J. Jasinski, M. Benamara, Z. Liliental-Weber, and R. J. Molnar, "Evolution of deep centers in GaN grown by hydride vapor phase epitaxy", *Appl. Phys. Lett.* **78**, 332 (2001). Jan01
9. A. Saxler, D. C. Look, S. Elhamri, J. Sizelove, W. C. Mitchel, C. M. Sung, S. S. Park, and K. Y. Lee, "High mobility in n-type GaN substrates", *Appl. Phys. Lett.* **78**, 1873 (2001). Mar01
10. A. Saxler, D. C. Look, S. Elhamri, J. Sizelove, D. Cull, W. C. Mitchel, M. Callahan, D. Bliss, L. Bouthillette, Sheng-Qi Wang, C. M. Sung, S. S. Park, and K. Y. Lee, "High Electron Mobility in Free-Standing GaN Substrates", *Mater. Res. Soc. Symp. Proc.* **639**, G7.2.1 (2001). Oct01
11. Z.-Q. Fang, D. C. Look, P. Visconti, D.-F. Wang, C.-Z. Lu, F. Yun, H. Morkoç, S. S. Park and K. Y. Lee, "Deep centers in a free-standing GaN layer", *Appl. Phys. Lett.* **78**, 2178 (2001). Apr01

12. D.C. Look, J.E. Hoelscher, J.L. Brown, and G.D. Via, "Electrical Profiles in GaN/Al<sub>2</sub>O<sub>3</sub> Layers with Conductive Interface Regions", *MRS Internet J. Nitride Semicond. Res.* **6**, 10 (2001). May01
13. S.H. Goss, X.L. Sun, A.P. Young, L.J. Brillson, D.C. Look, and R.J. Molnar, "Microcathodoluminescence of Impurity Doping at GaN/sapphire Interfaces", *Appl. Phys. Lett.* **78**, 3630 (2001). June01
14. D.C. Look and Z-Q. Fang, "Characterization of Near-Surface Traps in Semiconductors: GaN", *Appl. Phys. Lett.* **79**, 84 (2001). July01
15. D.C. Look and J.R. Sizelove, "Predicted Maximum Mobility in Bulk GaN", *Appl. Phys. Lett.* **79**, 1133 (2001). Aug01
16. D.C. Look, "Defect-Related Donors, Acceptors, and Traps in GaN", *phys. stat. sol. (b)* **228**, 293 (2001). Nov01
17. X.L. Sun, S.H. Goss, L.J. Brillson, D.C. Look, and R.J. Molnar, "Electronic defect states observed by cathodoluminescence spectroscopy at GaN/sapphire interfaces", *phys. stat. sol. (b)* **228**, 441 (2001). Nov01
18. K. Saarinen, T. Suski, I. Grzegory, and D. C. Look, "Ga vacancies in electron irradiated GaN; stability and temperature dependence of positron trapping", *Physica B* **308**, 77 (2001). Dec01
19. A.Y. Polyakov, N.B. Smirnov, A.V. Govorkov, Z-Q. Fang, D.C. Look, R.J. Molnar, and A.V. Osinski, "Deep hole traps in n-GaN films grown by hydride vapor phase epitaxy", *J. Appl. Phys.* **91**, 6580 (2002). May02
20. X.L. Sun, S.H. Goss, L.J. Brillson, D.C. Look, and R.J. Molnar, "Depth dependent investigation of defects and impurity doping in GaN/sapphire using scanning electron microscopy and cathodoluminescence spectroscopy", *J. Appl. Phys.* **91**, 6729 (2002). May02
21. G.G. Sim, P.W. Yu, D.C. Reynolds, D.C. Look, S.S. Kim, and D.Y. Noh, "Layer thickness dependence of strain in GaN grown by HVPE", *Mat. Res. Soc. Symp. Proc.* **693**, 171 (2002). July02
22. Z-Q. Fang, D.C. Look, P. Visconti, C. Lu, D. Wang, H. Morkoc, S.S. Park, and K.Y. Lee, "Characteristics of deep traps in freestanding GaN", *Mat. Res. Soc. Symp. Proc.* **693**, 455 (2002). July02
23. D.C. Look, R.L. Jones, X.L. Sun, L.J. Brillson, J.W. Ager III, S.S. Park, J.H. Han, R.J. Molnar, and J.E. Maslar, "Electrical and optical properties of GaN/Al<sub>2</sub>O<sub>3</sub> interfaces", *J. Phys.: Condensed Matter* (in press).

24. A.Y. Polyakov, A.V. Govorkov, N.B. Smirnov, Z-Q. Fang, D.C. Look, S.S. Park, and J.H. Han, "Microcathodoluminescence and electron beam induced current observation of dislocations in freestanding thick n-GaN sample grown by hydride vapor phase epitaxy", J. Appl. Phys. (in press).
25. A.Y. Polyakov, N.B. Smirnov, A.V. Govorkov, Z-Q. Fang, D.C. Look, S.S. Park, and J.H. Han, "Deep electron and hole traps in freestanding n-GaN grown by hydride vapor phase epitaxy", J. Appl. Phys. (in press).