

**REPORT DOCUMENTATION PAGE**

*Form Approved  
OMB No. 0704-0188*

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

**PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**

1. REPORT DATE (DD-MM-YYYY) 10 May 2004	2. REPORT TYPE Technical Paper	3. DATES COVERED (From - To) NA
--	-----------------------------------	------------------------------------

4. TITLE AND SUBTITLE Strongly Modulated Photonic Crystal with Tailor Made Negative Refractive Index	5a. CONTRACT NUMBER
	5b. GRANT NUMBER F33615-01-1-1007
	5c. PROGRAM ELEMENT NUMBER 61102F

6. AUTHOR(S) P. Vodo, V. Parimi, W.T. Lu, S.Sridhar, Northeastern University R. Wing, Air Force Research Laboratory	5d. PROJECT NUMBER 2305
	5e. TASK NUMBER GN
	5f. WORK UNIT NUMBER 02

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Northeastern University 360 Huntington Ave, Boston, MA 02115 R. Wing, Air Force Research Laboratory, 12 Skytop Rd, Ipswich, MA 01938-1449	8. PERFORMING ORGANIZATION REPORT NUMBER
--	--

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Research Laboratory 80 Scott Drive Hanscom AFB, MA 01731-2909	10. SPONSOR/MONITOR'S ACRONYM(S)
	11. SPONSOR/MONITOR'S REPORT NUMBER(S)

12. DISTRIBUTION/AVAILABILITY STATEMENT  
Unlimited

13. SUPPLEMENTARY NOTES  
Paper was cleared by Hanscom Public Affairs Office, 10 May 2004, Control Number 04-0489

14. ABSTRACT  
Negative refraction and left-handed electromagnetism in a metallic photonic crystal (PC) wedge are demonstrated in free space for both transverse magnetic and electric mode propagation. The experimental results are in excellent agreement with numerical calculations based on the band structure with no fit parameters used in modeling. The results demonstrate precision control on the design and fabrication of the PC to achieve tailor-made refractive indices between -0.6 to +1.

**DISTRIBUTION STATEMENT A**  
Approved for Public Release  
Distribution Unlimited

**20040623 015**

15. SUBJECT TERMS  
Negative Refractive Index (NIM), Photonic Crystal (PC), Electromagnetic Material

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT U	b. ABSTRACT U	c. THIS PAGE U	UL	9	Richard Wing AFRL/SNHA 19b. TELEPHONE NUMBER (Include area code) 781-377-3764

# **Strongly Modulated Photonic Crystal with Tailor Made Negative Refractive Index**

P. Vodo, P. V. Parimi, W. T. Lu, and S. Sridhar<sup>1</sup>

Electronic Materials Research Institute and Physics Department, Northeastern University,

360 Huntington Avenue, Boston, MA 02115

R. Wing

Air Force Research Laboratories, Hanscom AFB, MA.

Negative refraction and left-handed electromagnetism in a metallic photonic crystal (PC) wedge are demonstrated in free space for both transverse magnetic and electric mode propagation. The experimental results are in excellent agreement with numerical calculations based on the band structure with no fit parameters used in modeling. The results demonstrate precision control on the design and fabrication of the PC to achieve tailor-made refractive indices between -0.6 to +1.

---

<sup>1</sup> s.sridhar@neu.edu

Left-handed electromagnetism and negative refraction have recently been observed in the microwave frequency range in composite metamaterials<sup>1</sup> made of split ring resonators and wire strips, and in PCs<sup>2,3</sup>. Negative refraction in Left-handed metamaterials (LHM), when used effectively, opens the door for new approaches to a variety of applications from microwave to optical frequencies. An interesting application of negative refraction is superlensing<sup>4</sup> effect by a flat lens with no curved surfaces that can potentially overcome the diffraction limit imposed by conventional lenses. Indeed a flat lens without optical axis has been fabricated<sup>5</sup> recently using a photonic crystal structure. However for device applications it is important to have control over material parameters to be able to design and predict material properties.

Both negative refraction and left-handed electromagnetism have been demonstrated in photonic crystals using a parallel plate waveguide<sup>6,7</sup>. The 2D parallel plate structures used in all previous experiments to demonstrate negative refraction confine the lefthanded material and lead to spurious edge effects as observed in Ref (6). Close to the surface of refraction, the emerging wavefronts interfere and a clear negatively refracted beam is difficult to observe. Also, the coupling of the photonic crystal modes with the incident wave is different for transverse magnetic (TM) and electric (TE) mode propagations and is not well achieved in parallel plates. In addition, bandwidth is a crucial element for device applications in a wide frequency range. It is therefore essential to investigate lefthanded electromagnetism and negative refraction in a photonic crystal suspended in free space for both TM and TE mode propagations.

In this letter we report negative refraction for both TM ( $\vec{E} \parallel$  to the rod axis) and TE ( $\vec{E} \perp$  to the rod axis) mode propagation, in a metallic PC prism suspended in free space. Results show that a PC can exhibit negative refraction with tailor made refractive indices in a large frequency range. The propagation in different bands of the PC can be tuned with frequency to obtain either negative or positive refraction. Thus the present tailor made PC can be utilized for a variety of applications.

The microwave photonic crystal consists of an array of cylindrical copper tubes of height 60 cm and outer radius 0.63 cm arranged on a triangular lattice. The ratio of the radius  $r$  to the lattice constant  $a$  was  $r/a = 0.2$ . Refraction experiments were performed in an anechoic chamber of dimensions  $5 \times 8 \times 4 \text{ m}^3$  to prevent reflections from the walls. A square X-band horn placed at 3 m from the PC acts as a plane wave source (Fig.1). Placing a piece of microwave absorber with a  $6 \times 6 \text{ inch}^2$  aperture in front of the PC narrows the incident beam. On the far side another square horn attached to a goniometer swings around in two-degree steps to receive the emerging beam. Refraction is considered positive (negative) if the emerging signal is received to the right (left) of the normal to the surface of refraction of the PC. Measurements were carried out with the incident wave vector  $\vec{k}_i$  along  $\Gamma \rightarrow M(0,1)$  direction of the first Brillouin zone of the PC and in both TM and TE modes. The angle of incidence  $\theta = 60^\circ$  for  $\Gamma \rightarrow M$  is chosen in order to minimize surface periodicity along the surface of refraction, thus eliminating higher order Bragg waves.

Fig 2a shows a plot of the transmitted intensity measured at different angles and incident frequencies for the TM mode propagation. As can be seen from the figure between 6 and 7.1 GHz the signal emerges on the positive side of the normal to the surface corresponding to positive refraction. No transmission is observed between 7.1 and 8.3 GHz. Above 8.3 GHz and 11 GHz two signals are observed on the positive and negative sides of the normal. The negatively refracted signal is strongest around 10.7 GHz and positively refracted signal around 8.6 GHz. Although both positively and negatively refracted signals are observed, with the increase in frequency positive signal gets weaker while negative signal gets stronger. The experimental refractive index  $n$  is obtained from applying Snell's law  $n = \sin(\theta_r)/\sin(\theta_i)$  to each emerging beam. The validity of Snell's law has been established earlier in metallic PCs (6).

We have also carried out measurements of refraction for TE mode propagation. The results for this mode are shown in Fig 2b. Here negative refraction is observed between 6.4 – 9.8 GHz and positive refraction between 9.8 -12 GHz. It is important to note that negative refraction is possible for both TM and TE modes; such a freedom in the choice of modes provides a crucial advantage of using the metallic PC over the split ring wire array metamaterial.

The physical principle behind the present results can be understood from the band structure of the metallic PC. We have calculated the band structure of the triangular lattice PC employing a standard plane wave expansion method using 2500 plane waves. The 2D band structures of both TM and TE are shown in Fig. 3. For a plane wave with incident wave vector  $\vec{k}_i$  and frequency  $\omega$  incident normally on an air-PC interface, the wave vector  $\vec{k}_f$  inside the PC is parallel or anti-parallel to  $\vec{k}_i$  as determined by the band structure (Fig. 4). For a general case the phase and group velocities in a medium are  $\vec{v}_p = (c/n_p)\hat{k}_f$  with  $\hat{k}_f = \vec{k}_f/|\vec{k}_f|$  and  $\vec{v}_g = \nabla_{\vec{k}}\omega$ . Note that the direction of the group velocity  $\vec{v}_g$  in an infinite PC coincides with that of the energy flow. Conservation of the  $\vec{k}_f$  component along the surface of refraction would result in positive or negative refraction, depending on whether  $\vec{k}_f$  is parallel or anti-parallel to group velocity.

The emerging beam can be written as  $\Psi_t = a_0 e^{i\vec{k}_{t0}\cdot\vec{r}} + a_1 e^{i\vec{k}_{t1}\cdot\vec{r}}$  where  $\vec{k}_{t0}$  and  $\vec{k}_{t1}$  represent the refracted wave vectors corresponding to the 0<sup>th</sup> and 1<sup>st</sup> order Bragg wave-vectors of the field inside the PC. Let the component of  $\vec{k}_t$  along the normal to the surface of refraction of the prism be  $k_{t\perp}$ . One has  $k_{t0\perp} = \sqrt{\omega^2/c^2 - k_f^2 \sin^2 \theta}$  and  $k_{t1\perp} = \sqrt{\omega^2/c^2 - (2\pi/a - k_f \sin \theta)^2}$  where  $\theta = \pi/3$  and  $a$  is the lattice periodicity. The parallel component is  $k_{t\parallel} = k_f \sin \theta$ . The refracted angle can be obtained from  $\theta_r = \tan^{-1}(k_{t\parallel}/k_{t\perp})$  for each beam.

From the band structure and the equi-frequency surfaces (EFS) for TM mode of propagation negative refraction is predicted for the second and third band regions, with positive refraction in the 1<sup>st</sup> band. In the 1<sup>st</sup> band between 6-7.1GHz the EFS move outward with increasing frequency, so that  $\vec{v}_g \cdot \vec{k}_f > 0$ . In the second band between 8.3-11 GHz, the EFS move inward with increasing frequency, consistent with  $n_p < 0$  corresponding to  $\vec{v}_g \cdot \vec{k}_f < 0$  ( $\vec{v}_g$  anti-parallel to  $\vec{k}_f$ ). The band gap is in the frequency range 7.1-8.3 GHz between the 1<sup>st</sup> and 2<sup>nd</sup> pass-bands and from 11-11.2 GHz between the second and third bands.

An effective refractive index can be defined  $n_p = \text{sgn}(\vec{v}_g \cdot \vec{k}_f) c |\vec{k}_f| / \omega$  and calculated from the band structure. The sign of  $n_p$  is determined from the behavior of the EFS. In Fig. 2a & b the refractive indices for various bands determined from the theory are plotted. *The close match between the theoretical predictions and experimental data is striking.* All the predicted features including band gap, negative and positive refraction are observed in the experiment. The degeneracy observed in the case of TE mode is due to multiple bands for a single frequency, which results in multiple propagation  $k$  vectors. It is an interesting observation that different intensities are associated with different propagation vectors for TE mode. For this mode and for  $\Gamma \rightarrow M$  propagation from Fig. 3 it can be seen that the higher the slope of the curve the more intense the beam.

A particular feature of interest is the bandwidth for negative refraction and lefthanded electromagnetism. From Fig. 2a & b it can be deduced that the bandwidth for TE mode is 42 % and for TM mode 27%. In comparison, a relatively weakly modulated dielectric PC has a bandwidth estimated to be 6%<sup>3</sup> which is very narrow and the experimentally obtained bandwidth for metamaterials<sup>1,8</sup> to date is only 10%<sup>8</sup>. The present bandwidths for both TE and TM modes are higher than that in metamaterial. Bandwidth puts stringent restrictions on the tunability and functional range of the devices based on the LHM. In particular in our recent work we have shown that in the LHM, electromagnetic (EM) wave propagation is slow with group velocity of  $0.02c$ <sup>9,10</sup> where  $c$  is the velocity of EM wave in vacuum. This slow group velocity combined with large bandwidth can be used for designing a delay line filter with a large pass band.

In the case of TE mode, for an angle of incidence of  $60^\circ$  the refractive index is found to vary from 0 to -0.48, which is a 200% change for a frequency change of 42%. Such a large  $dn/d\omega$  results in a large  $d\phi/d\omega$ , which can be used in designing ultra sensitive phase shifters.

In conclusion, negative refraction is demonstrated for both TM and TE mode propagation in a metallic PC. Almost 400% improvement in the bandwidth for negative refraction is obtained for TE mode propagation in this tailor made PC. The strong dispersion observed results in a change of 200% in the negative refractive index for a frequency change of 42%. The ease and low cost of fabrication of the metallic PC vis- a-vis a dielectric PC and metamaterials make them ideal for a wide range of applications. Precise control over the geometry, choice of mode and scalability to submicron dimensions of PCs shows promise for applications from microwave to optical frequencies.

We thank John Derov and Beverly Turchenetz for invaluable contributions. The Air Force Research Laboratories, Hanscom AFB and the National Science Foundation supported this work under contract #F33615-01-1-1007.

**Fig. 1 (a). Microwave free space refraction experiment set up in an anechoic chamber. Negative or positive refraction is determined from the direction of the emerging signal with the normal to the surface of refraction.**

**Fig. 2 [Color] (a) Plot of refracted wave intensity measured at various angles, for TM mode propagation. (b) Similar plot for TE mode. Note the negative and positive refraction observed in different bands. Circles: theoretically calculated refractive indices corresponding to 0<sup>th</sup> order Bragg wave, and stars 1<sup>st</sup> order Bragg wave, both of which match strikingly with the experimental results without any fitting parameters.**

**Fig. 3 Band structures of the triangular metallic PC for both TM (dashed lines) and TE (solid lines) propagation modes are presented.**

**Fig. 4 Directions of incident transmitted and refracted wave vectors, and group velocity inside the PC. Positive or negative refraction can be observed depending on whether**

$$\vec{v}_g \cdot \vec{k}_f > 0 \text{ or } \vec{v}_g \cdot \vec{k}_f < 0$$

- 
- <sup>1</sup> R. A. Shelby, D. R. Smith, and S. Schultz, *Science* **292**, 77 (2001).  
<sup>2</sup> M. Notomi, *Phys. Rev. B* **62**, 10696 (2002); *Opt. Quant. Elect.* **34**, 133 (2002).  
<sup>3</sup> C. Luo et al, *Phys. Rev. B* **65**, 201104(2002)  
<sup>4</sup> J. B. Pendry, *Phys. Rev. Lett.* **85**, 3966 (2000).  
<sup>5</sup> P. V. Parimi, et. al., *Nature* **426**, 404 (2003).  
<sup>6</sup> P. V. Parimi et al, *Phys. Rev. Lett.*, 92, 127401-1 (2004).  
<sup>7</sup> E. Cubukcu *et al*, *Nature* **423**, 604 (2003).  
<sup>8</sup> C. G. Parazzoli *et al*, *Phys. Rev. Lett.* **90**, 107401 (2003).  
<sup>9</sup> P.V. Parimi, P. Vodo, W.T Lu, J. S. Derov, B. Turchinets, and S. Sridhar to be published  
<sup>10</sup> E. Di Gennaro et al, to be published

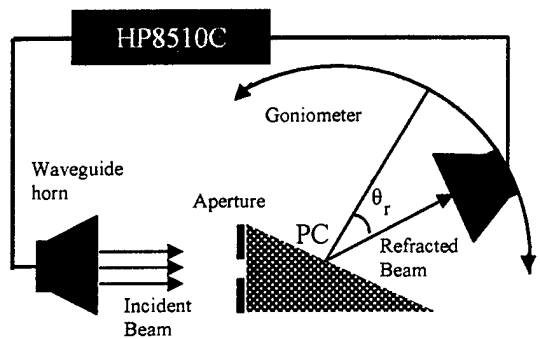


Fig.1 Vodo et al.

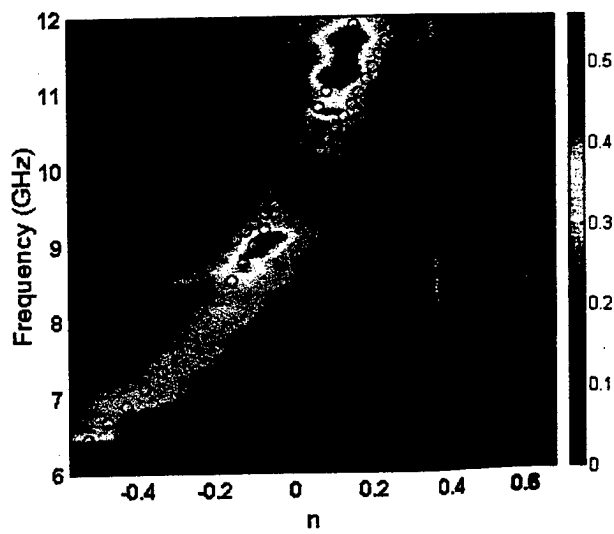
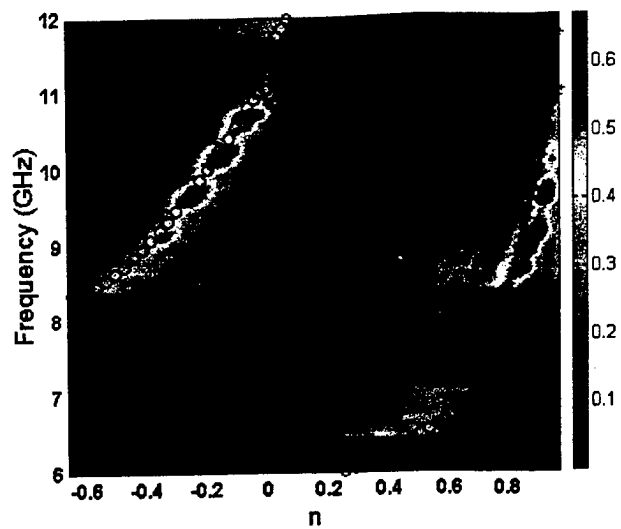


Fig.2 Vodo et al.

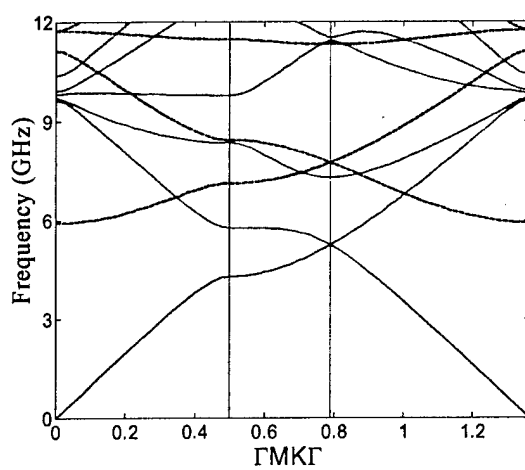


Fig.3 Vodo et al.

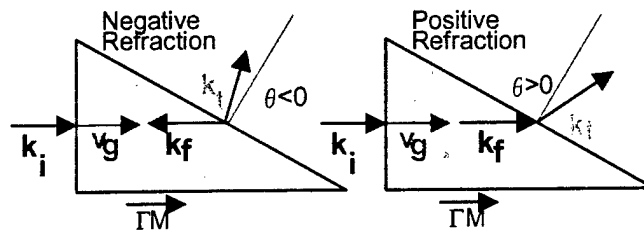


Fig.4 Vodo et al.