

Interfacial Synthesis of Electrically Conducting Polyaniline Nanofiber Composites

10 August 2004

Prepared by

A. R. HOPKINS,¹ D. D. SAWALL,² R. M. VILLAHERMOSA,¹
and R. A. LIPELES¹

¹Space Materials Laboratory
Laboratory Operations

²The University of Michigan
Ann Arbor, MI 48109

Prepared for

SPACE AND MISSILE SYSTEMS CENTER
AIR FORCE SPACE COMMAND
2430 E. El Segundo Boulevard
Los Angeles Air Force Base, CA 90245


Engineering and Technology Group

APPROVED FOR PUBLIC RELEASE;
DISTRIBUTION UNLIMITED

This report was submitted by The Aerospace Corporation, El Segundo, CA 90245-4691, under Contract No. FA8802-04-C-0001 with the Space and Missile Systems Center, 2430 E. El Segundo Blvd., Los Angeles Air Force Base, CA 90245. It was reviewed and approved for The Aerospace Corporation by P. D. Fleischauer, Principal Director, Space Materials Laboratory. Michael Zambrana was the project officer for the Mission-Oriented Investigation and Experimentation (MOIE) program.

This report has been reviewed by the Public Affairs Office (PAS) and is releasable to the National Technical Information Service (NTIS). At NTIS, it will be available to the general public, including foreign nationals.

This technical report has been reviewed and is approved for publication. Publication of this report does not constitute Air Force approval of the report's findings or conclusions. It is published only for the exchange and stimulation of ideas.


Michael Zambrana
SMC/AXE

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.				
1. REPORT DATE (DD-MM-YYYY) 10-08-2004		2. REPORT TYPE		3. DATES COVERED (From - To)
4. TITLE AND SUBTITLE Interfacial Synthesis of Electrically Conducting Polyaniline Nanofiber Composites		5a. CONTRACT NUMBER FA8802-04-C-0001		5b. GRANT NUMBER
		5c. PROGRAM ELEMENT NUMBER		5d. PROJECT NUMBER
		5e. TASK NUMBER		5f. WORK UNIT NUMBER
6. AUTHOR(S) A. R. Hopkins, D. D. Sawall, R. M. Villahermosa, and R. A. Lipeles		8. PERFORMING ORGANIZATION REPORT NUMBER TR-2004(8565)-7		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) The Aerospace Corporation Laboratory Operations El Segundo, CA 90245-4691		10. SPONSOR/MONITOR'S ACRONYM(S) SMC		
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Space and Missile Systems Center Air Force Space Command 2450 E. El Segundo Blvd. Los Angeles Air Force Base, CA 90245		11. SPONSOR/MONITOR'S REPORT NUMBER(S) SMC-TR-05-04		
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited.				
13. SUPPLEMENTARY NOTES				
14. ABSTRACT In this work, polyaniline/poly(sulfonated styrene) nanofiber composites were prepared by an interfacial method. The <i>in-situ</i> polymerization technique of these PANI nanofibers in the presence of sulfonated polystyrene allowed for the growth of PANI 2-D nanostructures embedded in the polymerized sulfonated host. This facile approach enables a self-assembly of these nanofibers into a workable, robust, conductive composite that can be processed and cast from water. A low accelerating voltage SEM was used to image these twisted fibers within the bulk of the cast film. In addition, the SEM confirmed the self-assembly of these 40-50 nm fibers within the host PSS to yield an electrically conducting composite film.				
15. SUBJECT TERMS nanocomposites, conducting polymers, polymer blends				
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES 11
a. REPORT UNCLASSIFIED	b. ABSTRACT UNCLASSIFIED	c. THIS PAGE UNCLASSIFIED		
				19b. TELEPHONE NUMBER (include area code) (310)336-5664

Acknowledgments

We wish to thank Dr. Nathan Presser (The Aerospace Corporation) for the SEM images and Professor Richard B. Kaner and Mr. Jiaying Huang for helpful discussions and insight on the interfacial polymerization of aniline.

Contents

1.	Introduction.....	1
2.	Experimental Details.....	4
	2.1 Electron Microscopy.....	4
	2.2 Electrical Conductivity.....	4
3.	Results and Discussion.....	6
4.	Conclusions.....	10
	References.....	12

Figures

1.	Snapshot of interfacial polymerization of aniline.....	6
2.	Optical and scanning electron microscopy (SEM) images of polyaniline nanofibers made by interfacial polymerization using (a) camphorsulfonic acid (CSA) and (b) sulfonated polystyrene (PSS) dopants.....	7
3.	Scanning electron microscope (SEM) images of 40% (wt/wt) polyaniline/poly(sulfonated styrene) (PANI-PSS) nanofiber composite synthesized by interfacial synthesis route.....	8
4.	Electrical dc conductivity as a function of PANI nanofiber concentration (wt/wt) in host PSS.....	9

1. Introduction

Electrically conducting polymers such as polyaniline (PANI) are viewed as 'organic metals' due to their metallic-like conductivity combined with the processability of organic polymers. The unique non-redox acid/base doping/dedoping chemistry of PANI and its consequence on structural, spectroscopic, and electronic transport properties allows PANI to be versatile in its end properties. It is well known that the design of the dopant not only increases electronic conductivity, but also alters electronic transport, processability, and optical properties. This 'dopant engineering' recently has shown to have consequences on polyaniline's morphology at the nano-scale. The method frequently employed to construct such morphologies has typically involved template-free chemical synthesis in which the aniline monomer polymerizes in the presence of large bulky acids. For instance, Huang et al.¹ recently developed a simple, practical method using a bi-phasic or "interfacial" polymerization for making uniform, template-free nanofibers. Furthermore, Wan et al.² developed a template-free solution method in which the diameter of the tube could be controlled by the dopant functionality and amount. Nanostructured polyaniline (nano-tube/wire/fiber/rod) is potentially useful in applications such as sensors and other nano-devices due to the advantages of both organic conductors and one-dimensional nanostructures.

While considerable effort has been expended toward the fabrication of these conducting polymer nanostructures, less attention has been paid in the literature to the processing of these nanofibers. The intractability of these polymer nanostructures, such as the nano/micro-tubes made by *in-situ* doping methods, presents limits to their processability. If polyaniline nanostructures can be made *in-situ* within a more processable host, conceptually it would eliminate the need for post-processing these nanostructures into a blend. This novel fabrication of electrically conducting nanocomposite preserves the integrity of the nanostructures without perturbing the electronic properties of polyaniline and the mechanical properties of the host polymer.

In this work, we have utilized the ability of PANI to form well-defined nanofibers to form a two-dimensional mesh of PANI fibers within an insulating host material. During the template-free interfacial polymerization¹ of these nanofibers, a macromolecular dopant [sulfonated polystyrene (PSS)] was chosen as both the host and dopant. The interfacial technique allows the formation of the nanofibers with diameters well below 100 nm. It is thought that the PSS protonates the aniline to yield anilinium ions, and during this polymerization, the 2-D nanofibers are ionically embedded in the polymerized sulfonated host. During polymerization, the PSS dopes the precipitated polyaniline nanofibers to yield the conducting salt; the resulting polystyrene sulfonate counter-anion also act as an imbedded host that is ionically attracted to the conducting nanofiber. This self-assembly technique allows for *in-situ* processing of these nanostructures in the host material. This facile approach to polymerizing PANI nanocomposites in the presence of sulfonated polystyrene is unique in that it yields well-defined 2-D nanofibers, as confirmed by scanning electron microscopy (SEM).

2. Experimental Details

PANI-PSS nanocomposites were synthesized by the following method: Predistilled aniline was dissolved in CCl_4 (A.C.S. Reagent, Aldrich Chemical) while ammonium peroxydisulfate (98%, Aldrich Chemical) was dissolved in water with 100 mol% poly(sulfonated styrene) (PSS) (Versa-TL 71, Alco Chemical) with a molecular weight of 70,000 g/mol. When transferred to a 200 mL beaker, an interface formed between the two immiscible solutions. Green polyaniline soon formed at the interface, then slowly migrated into the water layer. The entire water phase was finally filled with dark emeraldine green polyaniline polymerized in the presence of PSS. The by-products were removed from the aqueous phase using dialysis.

2.1 Electron Microscopy

Scanning electron microscopy (SEM) was used to examine the polyaniline/poly(sulfonated styrene) (PANI-PSS) nanofiber composite to identify the PANI nanostructured features within the embedded polystyrene. The JEOL 6401-F uses a cold-field emission electron source with a tungsten single-crystal tip. The sample chamber operated at a vacuum of 5.3×10^{-5} Pa. To prevent charging, a low accelerating voltage of 2 kV was used to image the conducting nanofibers. At such low accelerating voltage, it was not necessary to coat the polymer composite with any conducting layer, such as pyrolytic carbon or gold. A tip of less than 6×10^{-13} A allowed images up to 150,000x magnification at 2 kV without charging.

2.2 Electrical Conductivity

The films were deposited on an array of interdigitated gold electrodes on glass substrates fabricated at The Aerospace Corporation. The geometry of the electrodes consisted of 50 pairs of fingers, each finger having a dimension of $20 \times 4970 \times 0.18 \mu\text{m}^3$ with a $10\text{-}\mu\text{m}$ gap between fingers. The electrode array was mounted in a standard 24-pin dip package and wire bonded via gold contact pads. The resistances were measured with a Keithley 617 electrometer.

3. Results and Discussion

The formation of polyaniline nanofibers in the presence of poly(styrene sulfonic acid) (PSS) is illustrated in Figure 1. It is believed that the PANI nanofibers are formed at the interface where the aniline monomer and PSS meet. In this controlled, interfacial polymerization, the aniline is protonated by the PSS in the presence of the oxidant, ammonium persulfate. During this oxidative polymerization of aniline, the 100 % sulfonated polystyrene (an acidic, strong polyelectrolyte) acts as a proton source for the dopant and provides the necessary counterions to the developing charged polyaniline. In order for the interfacial polymerization to occur, the polyacid dopant must have a pK_a lower than that of the aniline monomer whose pK_a is 4.63. Note that the PSS maintains the water solubility of the final nanofiber composite complex. In this template-free synthesis, it is unclear what driving force(s) are involved in forming these nanofibers; however, it is hypothesized that there may be some preferential electrostatic alignment³ of the aniline monomer onto the anionic polyelectrolyte dopant

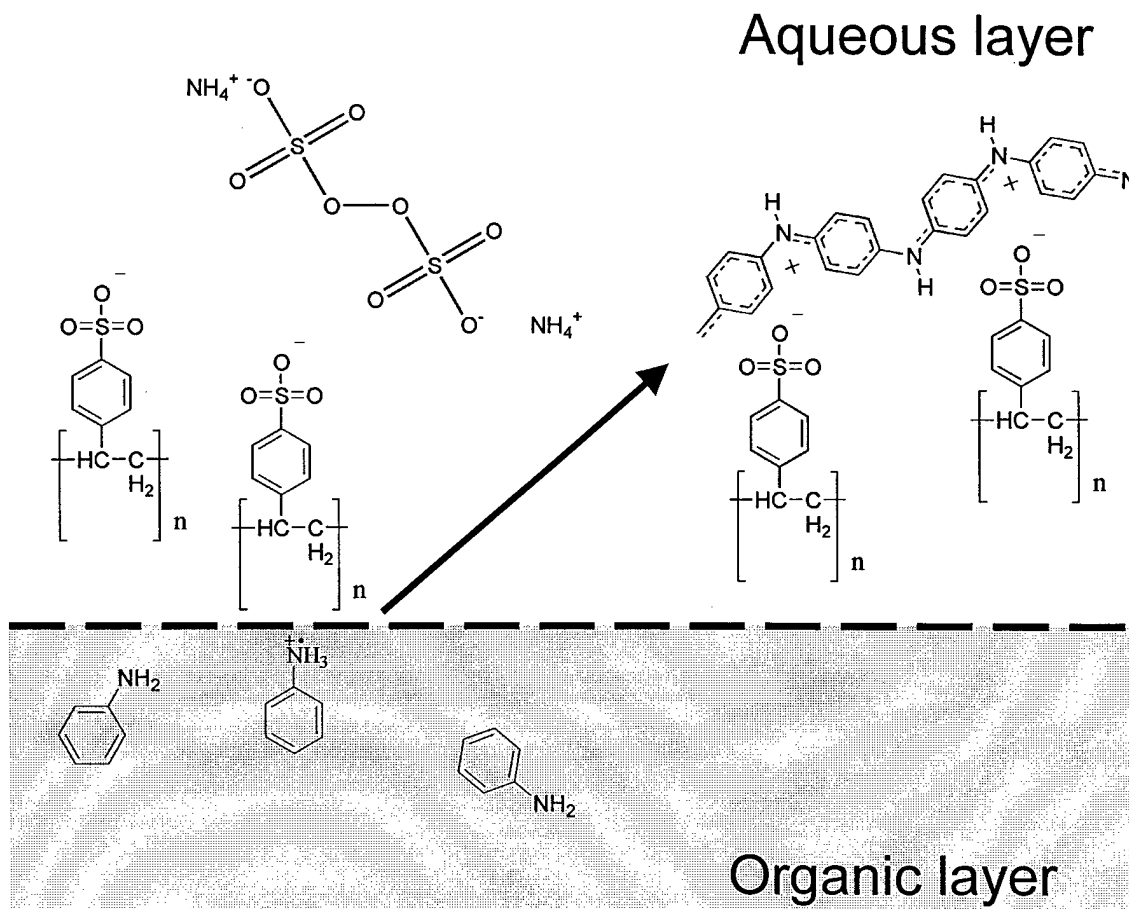


Figure 1. Snapshot of interfacial polymerization of aniline. The top layer is an aqueous solution of poly(styrene sulfonic acid) and ammonium peroxydisulfate, while the bottom layer contains dissolved aniline in CCl_4 .

(i.e., PSS), which is optimized by the interfacial method. Liu, et al.³ argued that the interface between the immiscible organic/aqueous system acts as a template that preferentially organizes the aniline monomer prior to polymerization. It is thought that as the aniline monomer is protonated on the surface, its head-to-tail coupling forms a low-energy helical structure when polymerized and precipitated into the aqueous phase of the biphasic system.

As the polymerization time increases to 15 min, a dark-green precipitate is seen to form in the top aqueous layer and deepens in both intensity and color after 25 min. The nanofibers imbedded in PSS yield a homogeneous dark-green complex after the by-products are removed. FTIR spectra of the polyaniline/poly(sulfonated styrene) (PANI-PSS) confirm the presence of doped polyaniline in the presence of the PSS host. In the nanofiber composite, benzenoid and quinoid ring vibrations were observed at 1500 cm^{-1} and 1600 cm^{-1} , respectively, confirming the oxidation state of PANI emeraldine salt. In addition, the broad band near 3400 cm^{-1} is assigned to the N-H stretching mode for PANI, while the strong band at 1150 cm^{-1} is an 'electronic-like' band considered to be a measure of the degree of delocalization of the electrons.^{6,7} No observed shift of these typical PANI peaks (compared to neat PANI) indicates that the individual components of the composite are preserved; thus, there is no mixing on the molecular level between PANI and PSS.

Although it has been clearly established in the literature⁸ that PANI nanotubes or nanofibers with diameters $<100\text{ nm}$ can be made, the novelty in this interfacial reaction is the substitution of a conventional doping acid with an acid-functionalized polymer. As seen in Figure 2-a, when camphorsulfonic acid (CSA) is the dopant in an interfacial polymerization route, one can obtain nanofibers with

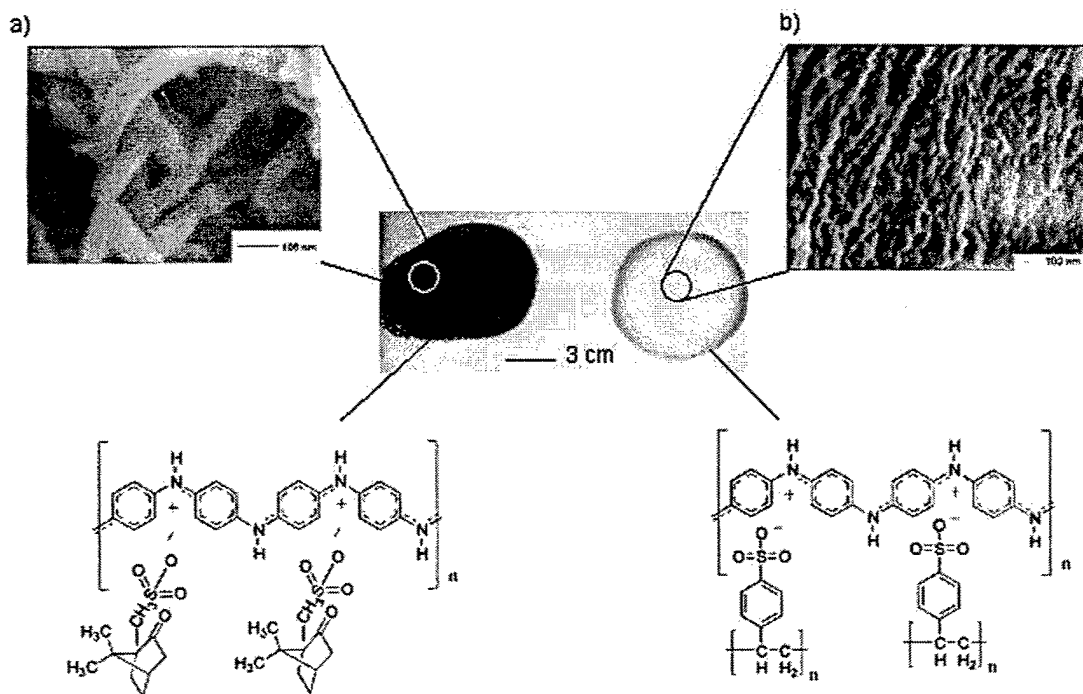


Figure 2. Optical and scanning electron microscopy (SEM) images of polyaniline nanofibers made by interfacial polymerization using (a) camphorsulfonic acid (CSA) and (b) sulfonated polystyrene (PSS) dopants.

diameters <50 nm. Substituting the molecular dopant, CSA, with a polymer dopant, PSS, the resulting material (Figure 2-b) is a processable, transparent, conductive film. The most important aspect of this procedure is the remarkable self-assembly of these nanofibers within the composite. As seen in the scanning electron microscope (SEM) micrograph in Figure 2, the nanofibers seem to form independent of the dopant functionality, which is consistent with the observations first made by Huang et al.⁸

Individual nanofibers of the PANI-PSS composite were imaged using a microscope that has a low accelerating voltage of 2 kV to avoid charge build-up on the film surface. Figure 3-a is a macro view of the water-cast film that shows gross cracking in the bulk of the film due to very rapid evaporation of water in the vacuum oven. The PANI nanofibers (light color) were not seen on the film surface and were only visible in the bulk of the polymer composite. Probing inside the bulk of the material through the cracks (Figures 3-b, -c, and -d), the SEM reveals 40–50 nm 2-D nanofibers imbedded in the low-emissive polystyrene. The density of the nanofibers appears to be higher in the center of the film and the lengths of these fibers range from 400 nm to a few micrometers. As compared with the neat nanofibers prepared in the presence of a camphorsulfonic acid, the composite nanofibers reveal a twisted surface, which is in contrast to the uniform surface in the PANI-CSA nanofibers (Figure 2-a).

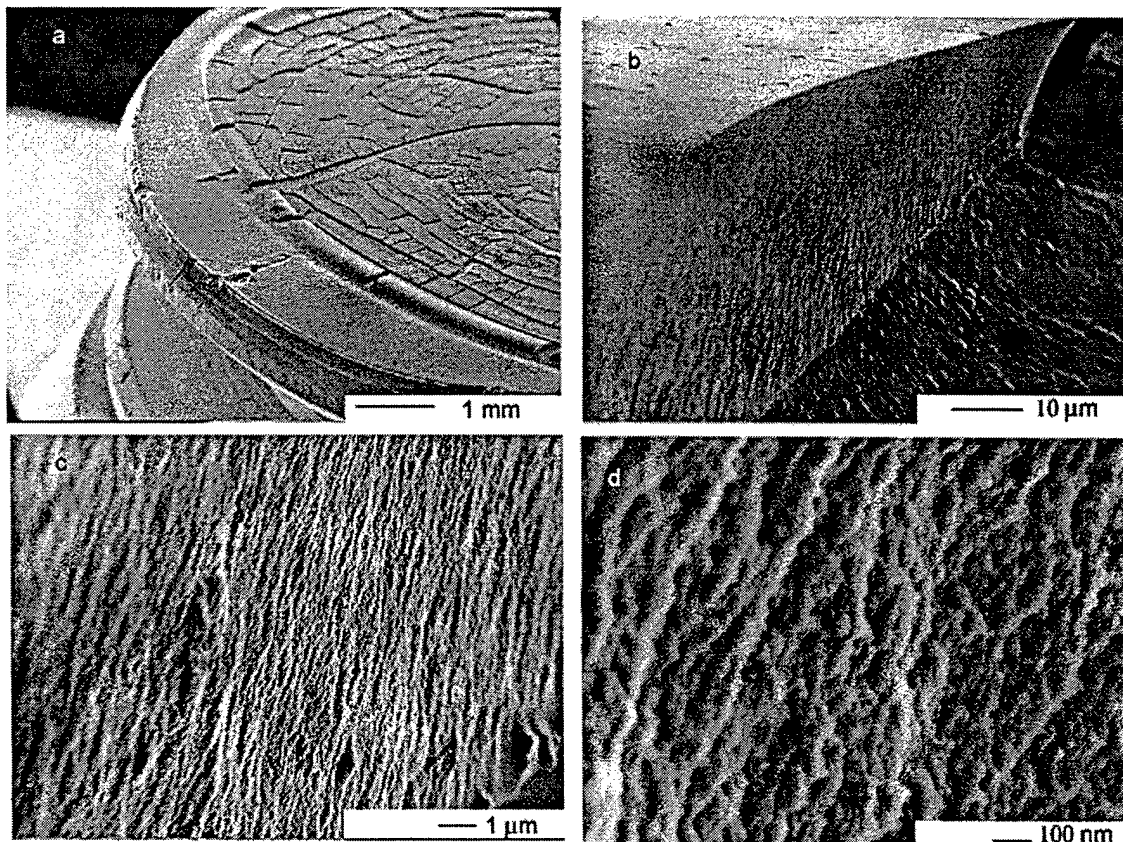


Figure 3. Scanning electron microscope (SEM) images of 40% (wt/wt) polyaniline/poly(sulfonated styrene) (PANI-PSS) nanofiber composite synthesized by interfacial synthesis route: (a) cracked film, (b) view inside a crack, exposing the bulk of the composite film to show (c) and (d) PANI nanofibers (light color) seen in wall of nanocomposite (50 nm in diameter) surrounded by the insulating, low-emissive (dark color) host PSS.

The intimate PSS coating of the aniline nanofiber as it develops in the aqueous phase of the biphasic polymerization is thought to increase the compatibility and stability of the resulting composite. In the nanofiber composite, the individual chains are molecularly wrapped with high molecular weight PSS, which acts to both stabilize the charge carriers on the PANI chains and provides a matrix in which the nanofibers are imbedded. This network ordering is analogous to previously reported blend systems⁹ where the connectivity of the conducting PANI salt becomes more ordered due to the crystallization of a host polymer, which yields higher conductivity values versus its amorphous counterpart. However, the ordering in these nanocomposites is not due to the crystallization of the host, but rather the result of a template-free polymerization of the aniline in the presence of the host.

Electrical conductivity has been shown to be sensitive to the morphology of a conducting polymer.¹⁰ To determine the dependence on conductivity of incorporating PSS in the presence of the growing PANI nanofiber, we have examined composites over the composition range of 0–55 % (wt/wt). As shown in Figure 4, PANI-PSS nanocomposites show a gradual increase in conductivity over the increasing PANI weight fraction interval with no sharp indication of a percolation threshold. The absence of a true percolation threshold is indicative of the overpopulation of acid groups compared with the limited number of imine nitrogen sites on the PANI tubes. The abundance of PSS is manifested in its ability to promote molecular compatibility between the two components and also acts to stabilize the electrical conductivity by reducing the doping acid's mobility within the composite. At relatively high concentrations (i.e., 10 %) of imbedded PANI nanofibers, both the optical properties and conductivity are in useful ranges for applications that include electromagnetic shielding and static charge dissipation.

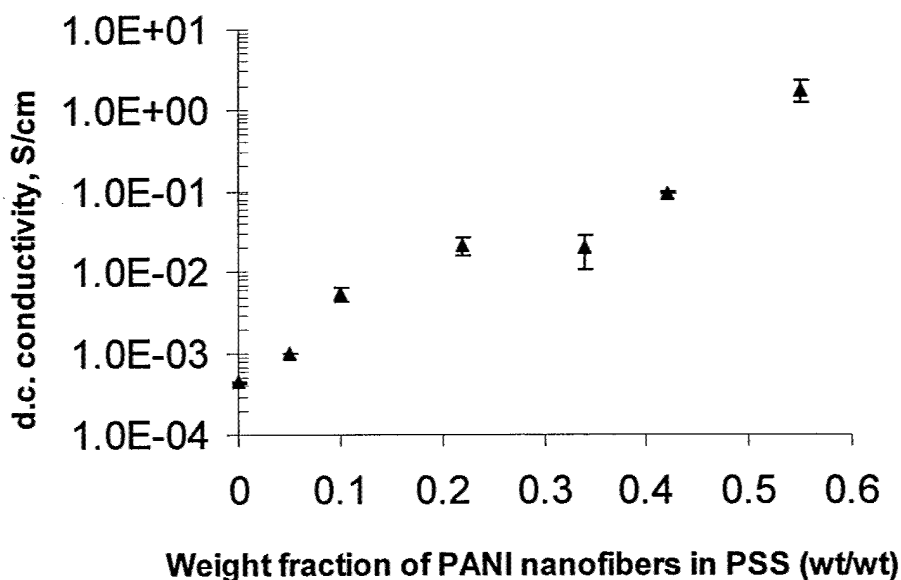


Figure 4. Electrical dc conductivity as a function of PANI nanofiber concentration (wt/wt) in host PSS. Composite concentration range of 0–55 % (wt/wt) loading PANI.

4. Conclusions

Polyaniline/poly(sulfonated styrene) nanofiber composites have been prepared by an interfacial method. The *in-situ* polymerization technique for the preparation of these PANI nanofibers in the presence of sulfonated polystyrene allows for the growth of PANI 2-D nanostructures. This facile approach enables a self-assembly of these nanofibers into a workable, robust, transparent conductive composite that can be processed and cast from water. The mechanism for this growth is believed to involve some alignment of the aniline monomer onto the anionic dopant, which is optimized by the interfacial method. This method of synthesizing conductive, transparent nanocomposites represents a unique approach utilizing the processability of host polymer and the self-assembly of these 40–50 nm PANI fibers within the composite.

References

1. J. Huang, S. Virgi, B. H. Weiller, and R. B. Kaner, *J. Am. Chem. Soc.*, 125 (2003), 314.
2. Z. Wei, Z. Zhang, and M. Wan, *Langmuir* 18 (2002), 917.
3. W. Liu, A. L. Cholli, and R. Nagaragan, *J. Am. Chem. Soc.* 121 (1999), 11345.
4. Z. Huseyin, *Polymer Preprints*, 44 (2003), 1104.
5. S. Quillard, G. Louarn, S. Lefrant, and A. G. MacDiarmid, *Physical Review B* 50 (1994), 12496.
6. Z. Huseyin, *Polymer Preprints*, 44 (2003), 1104.
- 7.S. Quillard, G. Louarn, S. Lefrant, and A. G. MacDiarmid, *Physical Review B* 50 (1994), 12496.
8. R.B. Kaner, and J. Huang, *J. Am. Chem. Soc.*, 126 (2004), 851.
9. A.R. Hopkins and J. R. Reynolds, *Macromolecules*, 33, (2000), 5221.
10. Y. Xia, and A. G. MacDiarmid, *Macromolecules* 27, (1994), 7212.

LABORATORY OPERATIONS

The Aerospace Corporation functions as an "architect-engineer" for national security programs, specializing in advanced military space systems. The Corporation's Laboratory Operations supports the effective and timely development and operation of national security systems through scientific research and the application of advanced technology. Vital to the success of the Corporation is the technical staff's wide-ranging expertise and its ability to stay abreast of new technological developments and program support issues associated with rapidly evolving space systems. Contributing capabilities are provided by these individual organizations:

Electronics and Photonics Laboratory: Microelectronics, VLSI reliability, failure analysis, solid-state device physics, compound semiconductors, radiation effects, infrared and CCD detector devices, data storage and display technologies; lasers and electro-optics, solid-state laser design, micro-optics, optical communications, and fiber-optic sensors; atomic frequency standards, applied laser spectroscopy, laser chemistry, atmospheric propagation and beam control, LIDAR/LADAR remote sensing; solar cell and array testing and evaluation, battery electrochemistry, battery testing and evaluation.

Space Materials Laboratory: Evaluation and characterizations of new materials and processing techniques: metals, alloys, ceramics, polymers, thin films, and composites; development of advanced deposition processes; nondestructive evaluation, component failure analysis and reliability; structural mechanics, fracture mechanics, and stress corrosion; analysis and evaluation of materials at cryogenic and elevated temperatures; launch vehicle fluid mechanics, heat transfer and flight dynamics; aerothermodynamics; chemical and electric propulsion; environmental chemistry; combustion processes; space environment effects on materials, hardening and vulnerability assessment; contamination, thermal and structural control; lubrication and surface phenomena. Microelectromechanical systems (MEMS) for space applications; laser micromachining; laser-surface physical and chemical interactions; micropropulsion; micro- and nanosatellite mission analysis; intelligent microinstruments for monitoring space and launch system environments.

Space Science Applications Laboratory: Magnetospheric, auroral and cosmic-ray physics, wave-particle interactions, magnetospheric plasma waves; atmospheric and ionospheric physics, density and composition of the upper atmosphere, remote sensing using atmospheric radiation; solar physics, infrared astronomy, infrared signature analysis; infrared surveillance, imaging and remote sensing; multispectral and hyperspectral sensor development; data analysis and algorithm development; applications of multispectral and hyperspectral imagery to defense, civil space, commercial, and environmental missions; effects of solar activity, magnetic storms and nuclear explosions on the Earth's atmosphere, ionosphere and magnetosphere; effects of electromagnetic and particulate radiations on space systems; space instrumentation, design, fabrication and test; environmental chemistry, trace detection; atmospheric chemical reactions, atmospheric optics, light scattering, state-specific chemical reactions, and radiative signatures of missile plumes.