

Dielectric Mixing Laws in Ceramic/polymer Composites

K. Yasuda*, Y. Sato, Y. Takahashi and T. Furukawa,

Faculty of Science, Tokyo University of Science, Shinjuku, 162-8601, Tokyo, Japan

ABSTRACT

Dielectric mixing laws were examined for the composites consisting of ferroelectric ceramics particles dispersed in the polymer matrix. The rate of increase in the dielectric permittivity with increasing ceramics content was shown to be consistent with classical Bruggeman predictions. The use of semiconductive polymer matrix generates dielectric as well as conductive relaxations associated with interfacial polarization. Analysis of the observed electrical spectra led to estimates of the dielectric permittivity of the ferroelectric ceramics particles. Discussion will be given with respect to the size effect on the dielectric response of the ferroelectric fine particles.

INTRODUCTION

When polymeric materials serve for practical uses, they are commonly mixed with other materials to achieve desired performance. Dielectric and conductive properties can be controlled over a broad range by inorganic inclusions. An introduction of ferroelectric ceramics power into a polymer matrix imparts piezoelectric and pyroelectric activities [1-3]. In this paper, we examine the composite consisting of barium titanate (BaTiO_3) particles and lithium perchlorate (LiClO_4)-doped polyethylene oxide (PEO) matrix. PEO and related polyethers have attracted great attention during the last two decades as solid-state electrolytes [4,5]. When a variety of metal-salts are added, they exhibit relatively high dc conductivity because dissociated ions gain mobility in accord with the segmental motion of polyether chains. BaTiO_3 is a typical ferroelectric having a high dielectric permittivity as well as large spontaneous polarization. Their composites show both dielectric and conductive characteristics and are expected to provide useful data for testing the mixing laws proposed earlier [6].

EXPERIMENTAL

The composite samples used in this investigation were prepared by mixing BaTiO_3 powders $3\mu\text{m}$, $1.4\mu\text{m}$, $0.7\mu\text{m}$ in diameter (Aldrich, milled) and $0.5\mu\text{m}$, $0.3\mu\text{m}$, $0.1\mu\text{m}$ in diameter (Sakai Chemical Ind. Co.Ltd., hydrothermally produced) into low molecular weight liquid PEO ($M=400$, Aldrich) in that $0.1\text{mol}\%$ LiClO_4 had been added. The maximum concentration of BaTiO_3 was 40% in volume. The samples thus prepared were sandwiched between $10\text{mm}\phi$ circular stainless steel electrodes using fused silica fiber spacer $125\mu\text{m}$ in diameter and were placed in a vacuum dielectric cell. Dielectric measurements were made over a broad frequency range ($10\text{mHz} - 13.5\text{GHz}$) to obtain the results in terms of either the complex permittivity or the complex conductivity. We also performed wide-angle X-rays measurements in order to investigate the fine structures of BaTiO_3 powder.

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 00 JUN 2003		2. REPORT TYPE N/A		3. DATES COVERED -	
4. TITLE AND SUBTITLE Dielectric Mixing Laws in Ceramic/polymer Composites				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Tokyo University of Science, Shinjuku, 162-8601, Tokyo, Japan				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release, distribution unlimited					
13. SUPPLEMENTARY NOTES See also ADM001697, ARO-44924.1-EG-CF, International Conference on Intelligent Materials (5th) (Smart Systems & Nanotechnology)., The original document contains color images.					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UU	18. NUMBER OF PAGES 4	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

Results and Discussion

Figure 1 shows the double logarithmic plots of the real components of the complex permittivity against frequency f for Li-PEO composites with $3\mu\text{m}$ diameter BaTiO_3 at 20°C . It is seen that ϵ' shows a three-step increase with decreasing f . The first increase near 1GHz is attributed to the segmental-mode relaxation of PEO molecules, the second near 10kHz to the interfacial polarization due to ions accumulated at the BaTiO_3 -PEO interface and the third to the electrode polarization. The value of ϵ' increases with increasing BaTiO_3 content above 1kHz and vice versa below 1kHz.

For quantitative analysis, we fitted the observed spectra to the empirical function

$$\epsilon = \epsilon_\infty + \frac{De}{(1 + (i\omega t)^b)^a} + De_{if} \left(1 - \frac{1}{1 + (i\omega t_{if})^{g_{if}}} \right) + \frac{s_{el}}{i\omega} \left(1 - \frac{1}{1 + (i\omega t_{el})^{g_{el}}} \right) \quad (1)$$

where ϵ_∞ is the instantaneous permittivity, De is the strength of segmental-mode relaxation, and De_{if} is the strength of interfacial polarization. An excellent agreement between observed and fitted spectra was confirmed by Fig.2.

The composite sample used here can be regarded as a two phase system where the spherical inclusions (BaTiO_3) are dispersed in a continuous matrix (Li-PEO). We then tried to reproduce the observed spectra using several mixing laws. The best reproduction was obtained by the use of a Bruggeman equation,

$$1 - f = \frac{\epsilon_2 - \epsilon}{\epsilon_2 - \epsilon_1} \left(\frac{\epsilon_1}{\epsilon} \right)^{\frac{1}{3}}, \quad (2)$$

where ϵ_1 is the permittivity of the matrix and ϵ_2 is that of inclusions. In our composite sample, ϵ_1 is the permittivity of pure Li-PEO, which is essentially a complex quantity containing dc conductivity

$$\epsilon_1 = \epsilon_\infty + \frac{De}{(1 + (i\omega t)^b)^a} + \frac{s_1}{i\omega}. \quad (3)$$

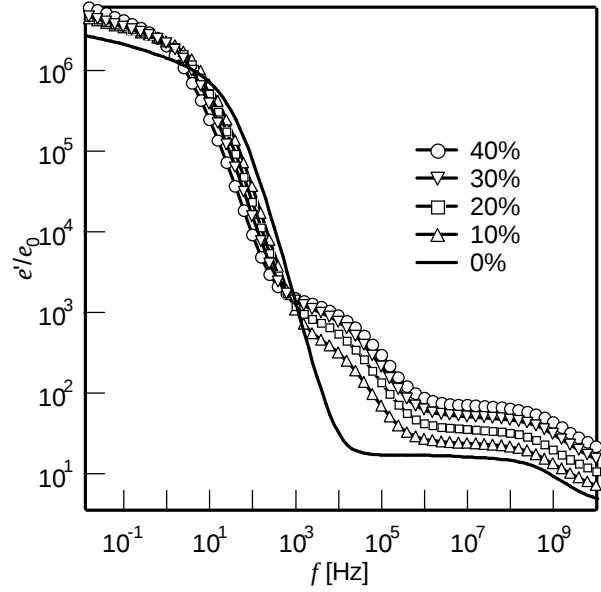


Fig.1 Dielectric spectra of $\text{BaTiO}_3/\text{Li-PEO}$ composites with $f=0, 0.1, 0.2, 0.3$ and 0.4 at 20°C .

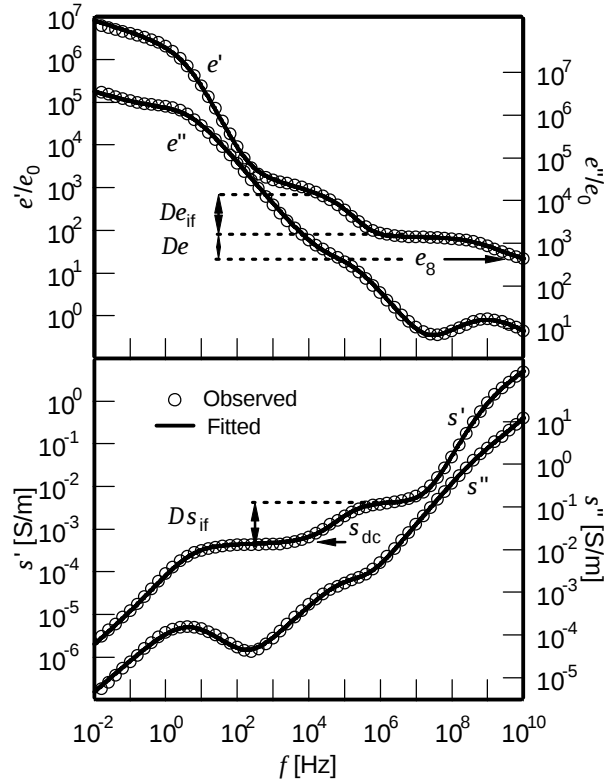


Fig.2 Observed and fitted dielectric and conductive spectra of $\text{BaTiO}_3/\text{Li-PEO}$ composites with $f=0.4$ at 20°C .

We determined the parameters comprising the above equation by the use of experimental data shown in Fig.1 ($f=0$). The permittivity of BaTiO₃ powder, ϵ_2 , is expected to be weakly dependent on frequency, but its value is unknown. We determined the value of ϵ_2 so that eq. (2) best-fits the observed spectra.

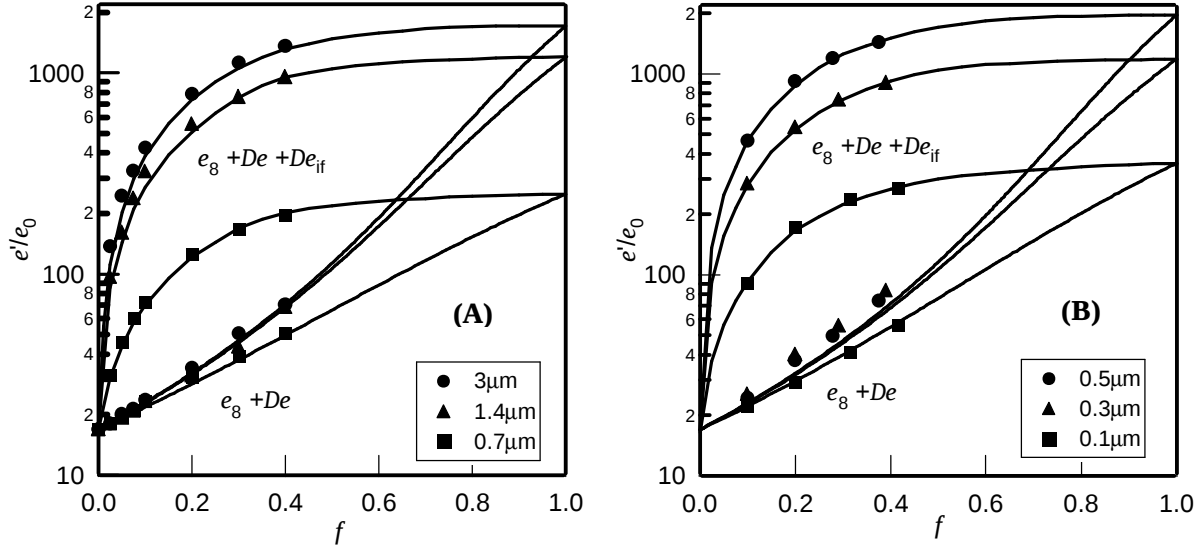


Fig.3 Dependence of observed and predicted permittivities of the composites on the volume fraction of BaTiO₃ powder produced by mill method (A) and hydrothermal synthesis (B.)

Figure 3 shows the dependence of observed and predicted permittivities on the volume fraction of BaTiO₃ f . We chose two permittivities, $\epsilon_8 + De$ containing contribution f segmental-mode relaxation and $\epsilon_8 + De + De_{if}$ with an additional contribution from the interfacial polarization. Their permittivities reach a unique value at $f=1$ which equals ϵ_2 . It is found that ϵ_2 strongly depends upon the particle size. It also depends upon the method of powder formation. The hydrothermally produced BaTiO₃ powder has much larger ϵ_2 than the milled one even though the particle size is equal.

We made X-ray measurements for these BaTiO₃ samples and found that the milled sample exhibits much broader diffraction pattern compared to the hydrothermally produced one. More importantly, the ratio of a and c axis of the tetragonal BaTiO₃ depends upon the particle size as well as the production method. We then plotted ϵ_2 against c/a and found a linear relationship as shown in Fig.4. These results indicate that the milled BaTiO₃ powder consists of small domains.

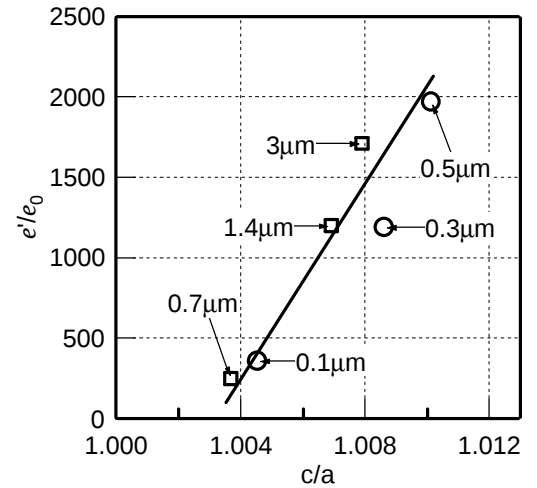


Fig.4 Linear relationship between the dielectric constant of BaTiO₃ powder and axis ratio c/a . (□ ; milled, ○ ; hydrothermal)

In the composite system consisting of ferroelectric ceramics powder dispersed in a polymer matrix, the former has much larger permittivity than the latter. Thus the effective permittivity of composite is primarily governed by that of the polymer phase and weakly depends upon that of the ceramic phase unless f is extremely high. In this investigation, we used

an ionically conductive polymer and found that the effective permittivity associated with the interfacial polarization accurately predicts the permittivity of ferroelectric ceramics powder. This finding would lead to a proposed for a useful technique that allows an accurate determination of the permittivity of ferroelectric nano-particles.

REFERENCES

- [1] D. K. Das-Gupta, "Piezoelectricity and pyroelectricity", Key Engineering Materials, **92-93**, 1 (1994).
- [2] T. Furukawa, K. Ishida, and E. Fukada, "Piezoelectric properties in the composite systems of polymers and PZT ceramics", J. Appl. Phys., **50**, 4094 (1979).
- [3] H. L. W. Chan, W. K. Zhang, Y. Zhang and C. L. Choy, "Pyroelectric and Piezoelectric properties of lead titanate/polyvinylidene fluoride-trifluoroethylene 0-3 composites", IEEE Trans. Dielec. Elect. Insul, **5**, 505 (1998).
- [4] M. B. Armond, J. M. Chabagno and M. J. Ducl ot, "Fast Ion Transport in Solids", Elsevier, Amsterdam, p133, 1979.
- [5] T. Furukawa, M. Imura and H. Yuruzume, "Broad-band conductive spectra of polypropylene oxide complexed with LiClO_4 ", Jpn. J. Appl.Phys., **36**, 1119 (1997).
- [6] D. A. G. Bruggeman, "Berechnung verschiedener physikalischer Konstanten von heterogonen Substanzen", Annalen der Physik, **24**, 636 (1935).