

AFRL-ML-WP-TP-2007-474

**DEVELOPING HIGH-TEMPERATURE
WATER-SOLUBLE COATINGS FOR
RECONFIGURABLE TOOLING
MATERIALS**



**George Calvert, Kevin J. Cao, Ted Jacobson, Linda Clements,
Shen-Yi Luo, Kwang J. Kim, and Brendan O'Toole**

JULY 2007

THIS IS A SMALL BUSINESS INNOVATION RESEARCH (SBIR) PHASE I PAPER.

Approved for public release; distribution is unlimited.

STINFO COPY

This work was funded in whole or in part by Department of the Air Force contract FA8650-06-M-5315. The U.S. Government has for itself and others acting on its behalf an unlimited, paid-up, nonexclusive, irrevocable worldwide license to use, modify, reproduce, release, perform, display, or disclose the work by or on behalf of the U. S. Government.

**MATERIALS AND MANUFACTURING DIRECTORATE
AIR FORCE RESEARCH LABORATORY
AIR FORCE MATERIEL COMMAND
WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7750**

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. **PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**

1. REPORT DATE (DD-MM-YY) July 2007		2. REPORT TYPE Conference Proceedings Preprint		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE DEVELOPING HIGH-TEMPERATURE WATER-SOLUBLE COATINGS FOR RECONFIGURABLE TOOLING MATERIALS				5a. CONTRACT NUMBER FA8650-06-M-5315	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER 65502F	
6. AUTHOR(S) George Calvert, Kevin J. Cao, and Ted Jacobson, (2Phase Technologies, Inc., Santa Clara, CA) Linda Clements (2Phase Technologies, Inc., Dayton, NV) Shen-Yi Luo and Kwang J. Kim (University of Nevada, Reno, NV) Brendan O'Toole (University of Nevada, Las Vegas, NV)				5d. PROJECT NUMBER 3005	
				5e. TASK NUMBER ML	
				5f. WORK UNIT NUMBER 912S1500	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) 2Phase Technologies, Inc. 2376 Walsh Avenue Santa Clara, CA 95051			8. PERFORMING ORGANIZATION REPORT NUMBER		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Materials and Manufacturing Directorate Air Force Research Laboratory Air Force Materiel Command Wright-Patterson AFB, OH 45433-7750			10. SPONSORING/MONITORING AGENCY ACRONYM(S) AFRL-MLMP		
			11. SPONSORING/MONITORING AGENCY REPORT NUMBER(S) AFRL-ML-WP-TP-2007-474		
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.					
13. SUPPLEMENTARY NOTES This is a Small Business Innovation Research (SBIR) Phase I Paper. PAO case number AFRL/WSC 07-1021, 24 April 2007. To be presented at the SAMPE Spring Technical Conference, Baltimore, MD, 01 June 2007. Paper contains color.					
14. ABSTRACT Report delivered under SBIR contract for topic AF06-115. High-Temperature water-soluble coatings are under development for the reformable state-change tooling materials of 2Phase Technologies' rapid, low-cost reconfigurable tooling systems (RTS). Such coatings can provide surface finish, impermeability, and improved structural properties for these materials. This paper describes the development of such coatings, including the investigation of chemical modification and mechanical reinforcement as well as the suitability of the coatings in elevated-temperature use. The coatings developed are based upon the same binder used for the tooling materials in the current commercial 2Phase reconfigurable tooling systems. Coatings solution properties, including solution density, pH values, and wet ability, were measured at different binder compositions. In addition, optical microscopy was employed to evaluate the coating texture. The paper describes the high-quality coatings obtained and the approach to further development.					
15. SUBJECT TERMS SBIR Report, coatings, affordability technology, tooling technology					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT: SAR	18. NUMBER OF PAGES 16	19a. NAME OF RESPONSIBLE PERSON (Monitor) DeAnna Brown 19b. TELEPHONE NUMBER (Include Area Code) (937) 255-7279
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			

Standard Form 298 (Rev. 8-98)
Prescribed by ANSI Std. Z39-18

To be presented at the SAMPE International Symposium in Baltimore, MD, June 2007.

DEVELOPING HIGH-TEMPERATURE WATER-SOLUBLE COATINGS FOR RECONFIGURABLE TOOLING MATERIALS

George Calvert, Kevin J. Cao¹, Ted Jacobson
2Phase Technologies, Inc
2376 Walsh Avenue, Santa Clara, CA 95051

Linda Clements
2Phase Technologies, Inc.
P.O. Box 730, Dayton, NV 89403

Shen-Yi Luo, Kwang J. Kim
Dept. of Mechanical Engineering
University of Nevada, Reno, Reno, NV 89557

Brendan O'Toole
University of Nevada, Las Vegas
Department of Mechanical Engineering
4505 Maryland Parkway, Las Vegas, NV 89154-4027

ABSTRACT

High-temperature water-soluble coatings are under development for the reformable state-change tooling materials of 2Phase Technologies' rapid, low-cost reconfigurable tooling systems (RTS). Such coatings can provide surface finish, impermeability, and improved structural properties for these materials. This paper describes the development of such coatings, including the investigation of chemical modification and mechanical reinforcement as well as the suitability of the coatings in elevated-temperature use. The coatings developed are based upon the same binder used for the tooling materials in the current commercial 2Phase reconfigurable tooling systems. Coating solution properties, including solution density, pH values, and wettability, were measured at different binder compositions. In addition, optical microscopy was employed to evaluate the coating texture. The paper describes the high-quality coatings obtained and the approach to further development.

KEY WORDS: Coatings, Affordability Technology, Tooling Technology

¹ Corresponding author. Email: kcao@2phasetech.com Phone: 408-450-7900 ext 113

1. INTRODUCTION

Reformable tooling systems are under development to permit rapid tooling modification and reconfiguration for rapid, low-cost open- or close-molding of composite materials and liquid resins. This technology relies upon 2Phase Technologies' patented state-change materials, which are liquid-particulate mixtures that can be changed from a formable (liquid-like) state to a force-resisting (solid) state, and then back to a formable state without change in volume.^[1,2] Once the desired tooling configuration is captured the water-based inorganic binder in these materials allows the tool to be "cured" at moderate temperature to produce semi-permanent tooling, and yet this cure can be reversed and the material reformed at any time by reinjection of the binder solution. This permits reconfiguration of the tool to accommodate design changes or for use of the tooling to make a completely different part.

Due to the porous surface of the tooling materials after cure, some type of liquid-resin impermeable layer or coating must be used to allow composite lay-up without penetration of the tooling material by the resin matrix. Thin elastomeric membranes have been the primary solution to date, but a desirable alternative is the development of a coating that, like the tooling material itself, will be reformable while still conferring resin impermeability. This paper describes the ongoing development of a water-soluble coating for the reformable state-change tooling materials used in a reconfigurable tooling system (RTS) and reports on the high-quality coatings developed to date.

Combining resin impermeability with the fact that coated 2Phase tooling materials will be used up to 400°C (750°F), coating development must take into account the following:

1. Solubility of the coating must be inhibited or calibrated to avoid depletion of the coating during "wet" cycles of the tooling material;
2. The coating must sustain precision tolerances through tool- and part-production cycles;
3. The coating must have high temperature resistance, a strong bond to the hardened particle/binder mix, and chemical and dimensional stability even after high temperature cycling;
4. The coefficient of thermal expansion (CTE) must match the substrate material in order to avoid delamination or cracking and to maintain dimensional tolerances;
5. The solubility after high-temperature exposure must be maintained so that the coating can be easily (preferably automatically) stripped from a fabricated shape;
6. The coating needs sufficient strength to withstand the pressure applied when fabricating composites;
7. The mechanical strength of the coating must be sufficient to avoid rupture during gelation and cure;

8. The coating must be impermeable to resin up to and at the working temperature; and
9. The coating needs to demold with a smooth surface and maintain smoothness during composite processing.

2. COATING DEVELOPMENT CONCERNS AND PROCEDURE

The same water-soluble binder already in use in the 2Phase reconfigurable tooling materials was used to develop coatings for the porous surface of the tooling materials.

2.1 Coating development concerns

2.1.1 *Trapped water and trapped air in the coating* The first factors that had to be considered in creating such a coating are the possibilities of water or air trapped in the coating.

There are three ways in which water can be trapped in the water-soluble binder: as free water, as secondary chemical-bonded water, or as primary chemical-bonded water. Most of the free water will evaporate or be removed by vacuum at room temperature; secondary chemical-bonded water can be removed by elevating the temperature; primary chemical-bonded water will be removed or remain depending upon the hydration state and will be released above some certain elevated temperature. As the temperature is increased during tooling material hardening or composite curing, any water still trapped in the coating may bubble and ruin the surface smoothness.

Similarly, air can be trapped in the binder, and any trapped air will also bubble as temperature is increased, ruining the surface smoothness. The problems with both trapped water and trapped air will become more severe the thicker the coating.

2.1.2 *Chemical modifiers* Two types of chemical modifiers were introduced. Chemical modifier I was a defoamer, which was used to reduce the amount of trapped air and decrease the generated bubble size. Chemical modifier II, a surfactant, was used to modify the wettability on a substrate as well as to shift the dehydration temperature.

2.1.3 *Glass microspheres* Glass microspheres improve the coating strength by mechanically reinforcing the coating. The average diameter of the glass microspheres used in the coatings was about 50 μm , which is much smaller than is used in the reconfigurable tooling materials themselves.

2.1.4 *Gelling agent* Gelling agents were introduced to retain moisture temporarily, make the coating more flexible and provide a barrier to inhibit coating dissolution. Both alcohol and acetate gelling agents were used.

2.1.5 *Substrate* 2Phase state-change materials were used as the substrate for all coating studies described in this paper. It should be noted that the water-soluble coating

was developed primarily for use on 2Phase tooling materials but could also be used in other coating applications.

2.2 Coating development procedure

2.2.1 Coating formula preparation First, assemble the 2Phase binder solution, chemical modifier I, chemical modifier II and glass microspheres in the proportions 100:1:1:50 by volume. Second, combine the coating binder, chemical modifier I and chemical modifier II and mix for 5 minutes by mixer at room temperature. Third, add the glass microspheres and mix for an additional ten minutes.

2.2.2 Mold preparation First, clean the mold with water to remove any inorganic dust on the mold surface, then clean with alcohol to remove any organic dust. Second, spray with a mold-release agent and dry the mold in a 65°C (150°F) furnace for 3 minutes.

2.2.3 Coating procedures Three coating methods were investigated:

2.2.3.1 Brush-on method, in which the coating is applied directly to a tool by brushing thin layers, with air drying in between, onto the finished, cured state-change material and then is post-cured to a hardened state;

2.2.3.2 Spray-on method without gelling agent, in which the coating is applied by spraying back and forth onto the finished, cured state-change material or into a mold that will be filled with state-change material. The spray passes continue until a 0.5-mm-thick coating is developed, and then the coating is air dried and subsequently post-cured to a hardened state;

2.2.3.3 Spraying method with gelling agent, in which the coating mixture is applied as in the previous method and then a gelling agent, which can be alcohol or acetate, is sprayed in a single sprayer pass onto the coating layer, followed by air drying and post-curing the combination coating to a hardened state.

3. MATERIALS PROPERTIES

3.1 Density and solid content Due to concerns about alkaline corrosion, pH control is necessary to extend the glass microsphere service life. Changes in binder concentrations in the coating solution change both the density and the pH of the coating solution. Figure 1 shows the relationship between solution density and both binder solid content and pH. Solution density was measured by a hydrometer. Based on measured density and the linear relationship between density and solid content, the solid content can be calculated by a curve fitting equation ($A=1.0158 \times \rho - 1.0351$, where A: solid content, ρ : solution density).

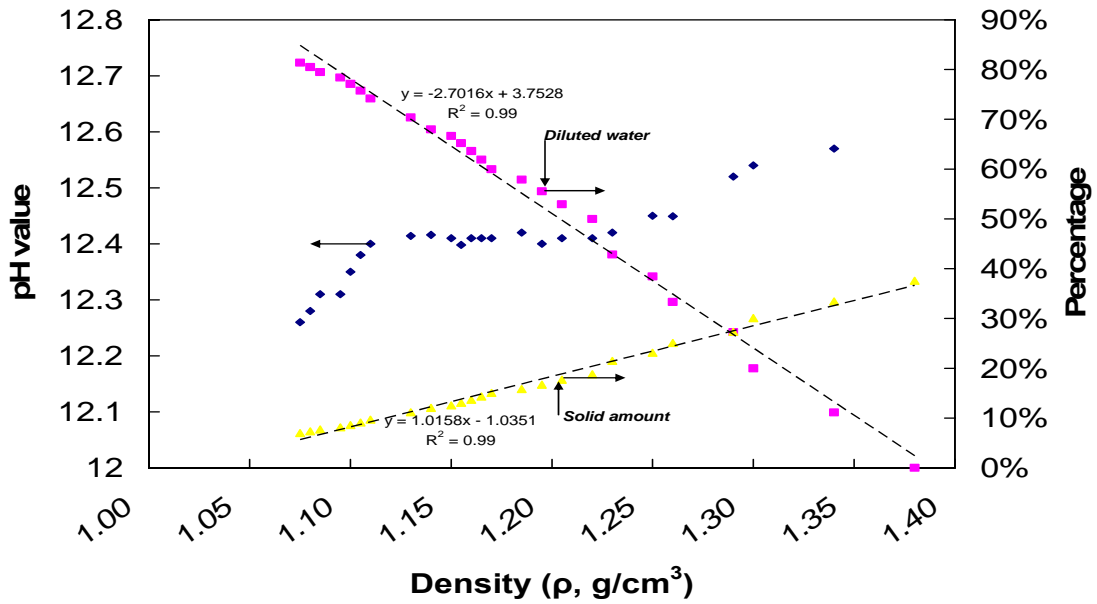


Figure 1. Solution density as a function of pH and increased binder concentration solids in 2Phase coating binder solution

3.2 **Wettability** A CAM 100 compact contact angle meter was employed to investigate the binder surface properties. Figure 2a shows the software interface and Figure 2b shows the wettability of different binder concentrations. The contact angle is found to decrease as binder concentration increases, indicating better wetting by the coating solution.

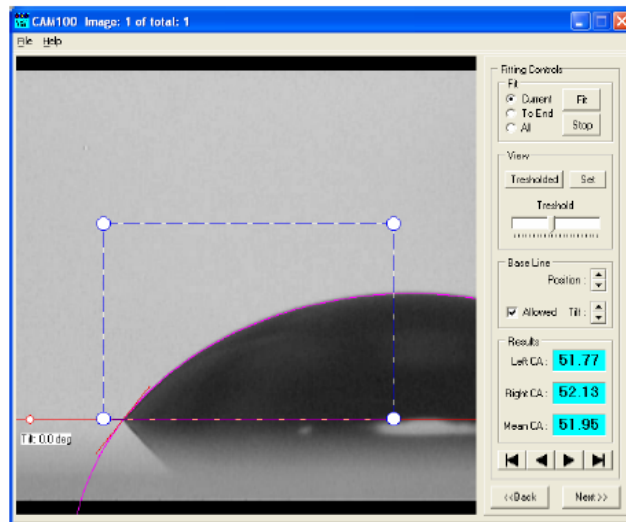


Figure 2a. Contact angle measurement software interface

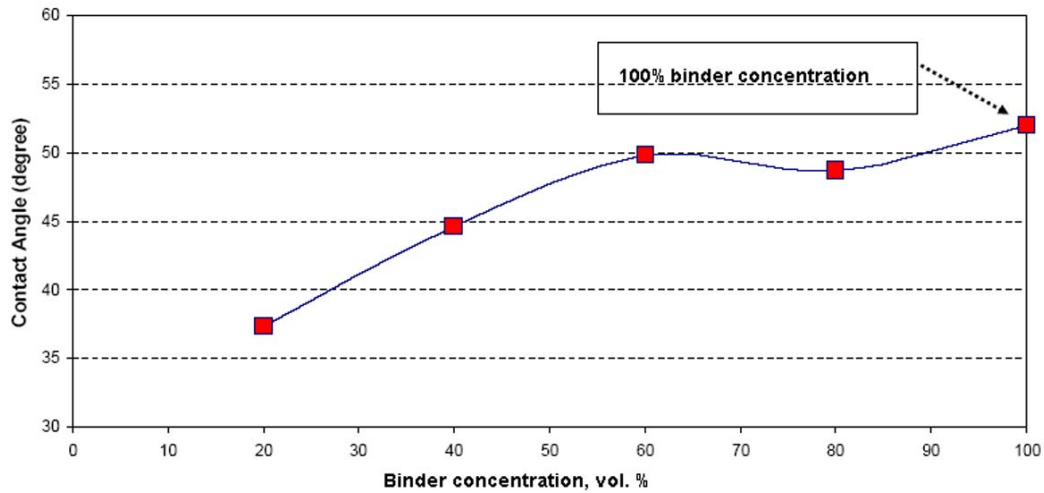


Figure 2b. Binder wettability at different binder concentrations.

4. RESULTS

4.1 Coated tools produced using three coating methods The results of the three coating procedures are shown in Figures 3, 4, and 5.

Figure 3 shows a tool coated using the brush-on method. The resulting coating is non-uniform and shows significant defects.

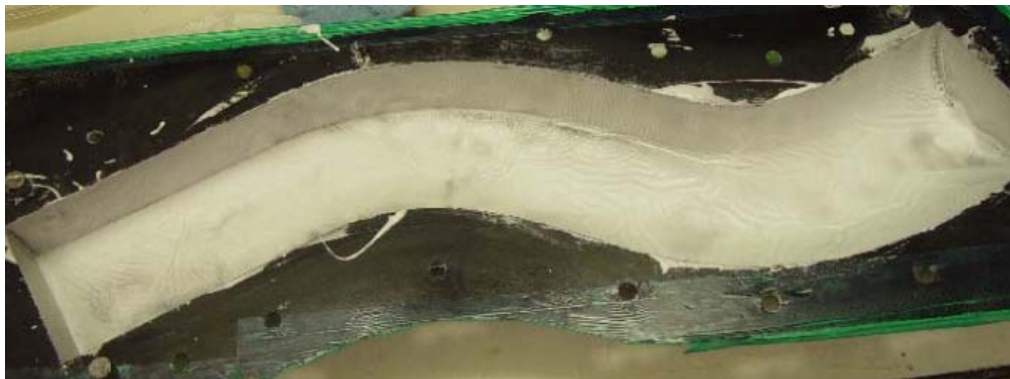


Figure 3: Coating applied to tooling by hand brushing

Figure 4 illustrates how the two spray-on methods were used to apply coatings to the tooling by applying them to a mold in which the tooling is to be formed. Figure 4a shows a mold that has been coated using the spray-on method without gelling agent, while Figure 4b shows a similar mold coated using the spray-on method with gelling agent.

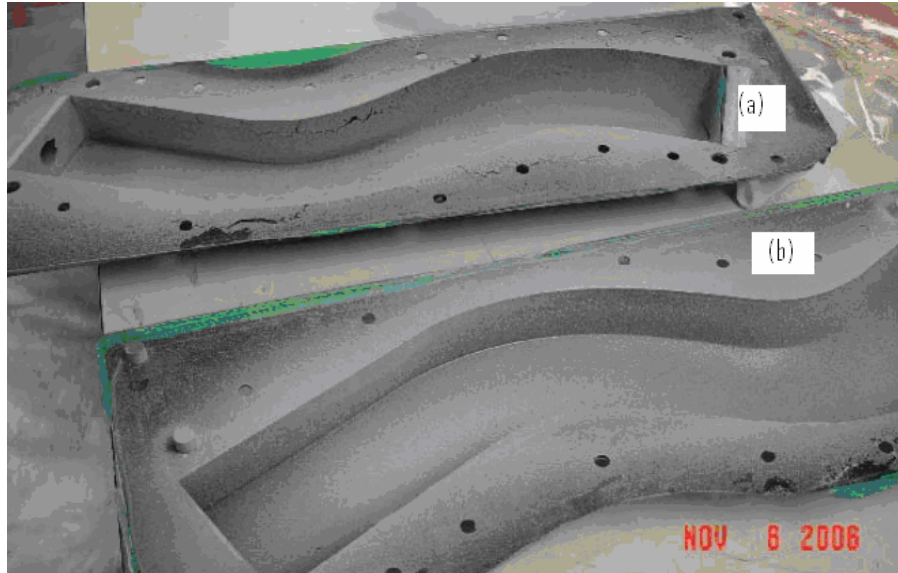


Figure 4. Coating applied to an inner mold by spray-on method: (a) spray-on and air-dry coating without alcohol gelling agent and (b) spray-on and air-dry coating with alcohol gelling agent

After the coating was applied to the inner mold, a slurry of the liquid-like tooling material was pumped in at one end of the mold while excess liquid was drained at the other end. The tool was then cured at 177°C (350°F) and 550 MPa (80 ksi) vacuum for six hours.

As shown in Figure 5a, the spray-on method with a gelling agent applied to the tooling mold surface generated a very smooth, glass-like coating surface. The gelling agent produces a polymerization reaction that changes the coating into a gel-like substance and reduces the solubility of the coating during the slurry-filling step. For the spray-on coating applied without the gelling agent, however, the coating material dissolved in the tooling material slurry during processing, leaving a rough, permeable surface as shown in Figure 5b(1). The brush-on method, as shown in Figure 5b(2), does not give a uniform coating on the outer surface. The spray-on method with gelling agent generated the best surface: a glass-like, smooth surface that is an exact match to the mold surface.



Figure 5: Trapped tooling with coatings: (a) shining surface resulting from tooling with spray-on coating method with gelling agent, and (b) comparison of three finished tools: (1) tool with spray-on coating without gelling agent, (2) tool with brush-on coating and (3) tooling with spray-on coating with gelling agent.

4.2 Optical microscopy Figure 6, taken by an optical microscope, shows a tooling surface with a coating produced by spraying-on with an alcohol gelling agent. The micrograph reveals that the coating is smooth, translucent and pinhole-free and is about 400 μm thick.



Figure 6: Optical micrograph of coating produced by spray-on with gelling agent on a tooling surface of 2Phase Technologies' reconfigurable tooling material.

4.3 Coating suitability for high-temperature usage To evaluate the suitability of the coatings for high-temperature use, portions of tooling specimens with coatings produced by the spray-on method with gelling agent were baked for six hours at 400°C (750°F), as shown in Figure 7. At this high temperature the coating changes to a whiter color but remains smooth and glass-like.

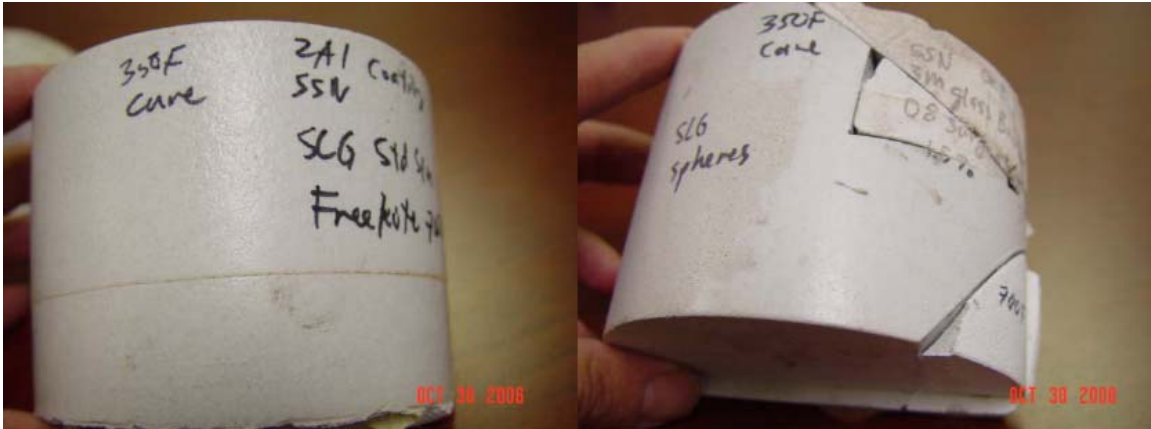


Figure 7. High temperature evaluation of 2Phase spray-on coating with gelling agent. Specimen on right was cured at 177°C (350°F) while sections of the specimen on the right, as marked, were removed and cured at 400°C (750°F).

The whitening is due to foaming in the binder, but chemical modification by chemical additives and mechanical reinforcement by glass microspheres can be used to decrease the foaming bubble size to a microscopic scale.

5. CONCLUSIONS AND FUTURE WORK

A high-temperature-capable, high-quality, water-soluble coating was successfully developed. Such coatings are of particular importance to provide surface finish, impermeability, and improved structural properties for reconfigurable tooling materials. Coating solution properties, including solution density, pH values, and wettability, were measured at different binder concentrations. Three different techniques for producing coatings were evaluated. Optical microscopy was employed to evaluate the resulting coatings. A spray-on technique using a gelling agent was found to produce a high-quality, pin-hole-free, glass-like coating surface.

Future work will include further investigation and development of coating formulations for elevated-temperature service, and development of coating techniques for production-level tooling.

6. REFERENCES

1. B. O'Toole, S. Rahman, J. Malpica, S. Raagas, K. Nelson, G. Calvert and L. Clements, "Micromechanics and Bulk Properties of a Porous State-Change Material", SAMPE International Symposium, **51**, (2006), CD-ROM.
2. K. Nelson, S. Rahman, S. Raagas, B. O'Toole, G. Calvert, L. Clements, "Characterization of State-Change Reconfigurable Tooling Materials", SAMPE International Technical Conference, **37**, (2005), CD-ROM.
3. Jingyao Cao, Leishan Chen, "Effect of thermal cycling on carbon fiber-reinforced PPS composites," *Polymer composites* **26**:55, 713-716 (2005).

7. ACKNOWLEDGEMENTS

This work was funded in-part by U.S. Air Force SBIR Phase I contract FA8650-06-M-5315.