



Fabrication and Characterization of Schottky Diodes using Single Wall Carbon Nanotubes

by Brandon E. Luquette and Barbara M. Nichols

ARL-TR-4534

August 2008

NOTICES

Disclaimers

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

Army Research Laboratory

Adelphi, MD 20783-1197

ARL-TR-4534

August 2008

Fabrication and Characterization of Schottky Diodes using Single Wall Carbon Nanotubes

Brandon E. Luquette and Barbara M. Nichols
Sensors and Electron Devices Directorate, ARL

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE (DD-MM-YYYY) August 2008		2. REPORT TYPE Final		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Fabrication and Characterization of Schottky Diodes using Single Wall Carbon Nanotubes				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Brandon E. Luquette and Barbara M. Nichols				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRD-ARL-SE-RL 2800 Powder Mill Road Adelphi, MD 20783-1197				8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TR-4534	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited.					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT Schottky diodes using single wall carbon nanotubes (SWNTs) were fabricated using palladium and aluminum source and drain contacts, respectively. SWNTs were grown on high resistivity silicon substrates with a thermal oxide layer using chemical vapor deposition and ferric nitrate catalyst. Multiple cleanroom processing steps were used to make the diodes which included the deposition of marker layers, oxygen plasma etch for selective nanotube removal, and electron beam evaporation of metal electrodes in two separate depositions. The diodes were designed in a coplanar waveguide (CPW) transmission line topology in order to facilitate RF testing. Electrical testing at the DC level was accomplished. Further investigation into the RF characterization of carbon nanotubes will allow for the incorporation of such devices into integrated circuit architectures.					
15. SUBJECT TERMS Carbon nanotubes, Schottky diodes					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT SAR	18. NUMBER OF PAGES 16	19a. NAME OF RESPONSIBLE PERSON Barbara M. Nichols
a. REPORT U	b. ABSTRACT U	c. THIS PAGE U			19b. TELEPHONE NUMBER (Include area code) 301-394-0602

Contents

List of Figures	iv
1. Background	1
2. Fabrication	2
3. Electrical Testing	5
4. Discussion	7
5. Conclusion	8
6. References	9
Distribution List	10

List of Figures

Figure 1. Band diagram illustrating Schottky barrier height dependence on the work function of metal contact. Diagram from reference 6.	2
Figure 2. SEM image of photoresist protected tubes after the photoresist was dissolved.	3
Figure 3. AFM images of metal contacts fabricated using standard photolithography showing the pronounced flashing at the edges.	4
Figure 4. (a) Diode layout: The inner electrode represents the signal electrode (red – Al). The outer electrodes represent the ground electrodes (black – Pd/Au), (b) SEM image of the diode layout, (c) Schematic picture of device setup, and (d) SEM image of electrode-nanotube interface (top contact: Pd/Au, bottom contact: Al).	5
Figure 5. Diode DC I-V curve showing both the forward characteristic and reverse breakdown. The turn on voltage for the device occurs at 1.1 V. The ideality factor for this device is 1.80.	6

1. Background

Semiconducting single wall carbon nanotubes (SWNTs) possess unique electrical properties including carrier mobilities unrivaled in state of the art semiconductors (1) and the ability to carry high current densities (2). The ability to control these properties holds the promise for smaller, faster, denser, and more power efficient electronics. Accompanying the potential for higher performance voltage controlled current, SWNTs present an opportunity for high frequency applications. In order to harness the capabilities of this technology, fundamental functional devices must be fabricated and characterized. One fundamental device in microelectronic design is the two-terminal rectifier – the diode. One subset of the diode, particularly of interest for RF (radio frequency) applications such as receiver systems, is the Schottky diode.

Functionally realizing the Schottky diode using SWNTs is accomplished by depositing two different metals with differing work functions onto the nanotube to serve as the source and the drain. The operation of the diode is dictated by the interface of the metal contact and the nanotube. A Schottky barrier is formed at this interface due to the differences in the metal Fermi level and the valence/conduction band of the nanotube (3). The height of this barrier is dependent upon the work function of the metal used for the contact (4). By using a metal with a higher work function as a contact at one end of the nanotube, an ohmic contact is created. On the other end of the device, a metal with a lower work function than the nanotube is used to create a Schottky contact. The band diagram in figure 1 represents the device under forward bias. E_C is the conduction band edge, E_V is the valence band edge, and Pd and Al represent the relative work functions of palladium and aluminum with respect to the nanotube. Note SWNTs usually act as p-type semiconductors.

Electron transport through the barrier is achieved by thermionic emission (TE) as well as tunneling current. The TE current produces the rectifying I-V curve and dominates electron transport when the device is not gated (5). When a voltage is applied across the device, positive or negative depending on the channel doping, electron emission is increased due to increased electron energy, and current flow is established.

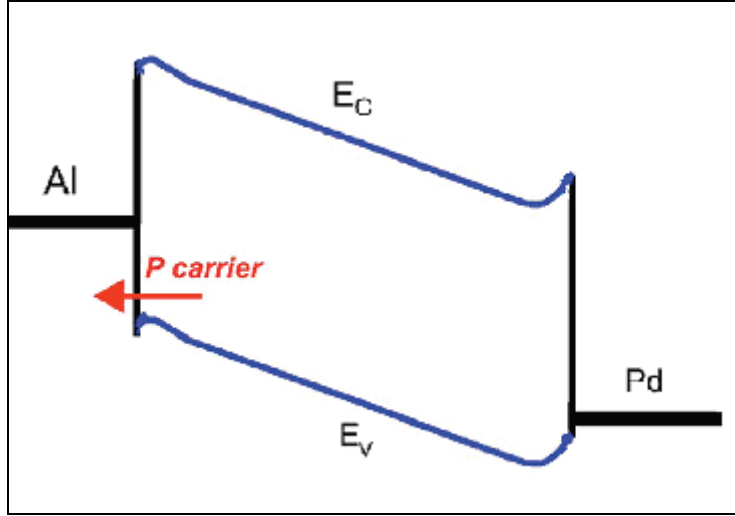


Figure 1. Band diagram illustrating Schottky barrier height dependence on the work function of metal contact. Diagram from reference 6.

2. Fabrication

The Schottky device fabrication layout consisted of 4 different photomask layers designed in collaboration with the Fuhrer research group at the University of Maryland. The first layer consisted of alignment markers for processing subsequent layers. The marker layer consisted of 10 Å titanium covered by 1000 Å of platinum. All metal deposition was done by e-beam evaporation. This metallization was chosen specifically to withstand the high temperatures of carbon nanotube growth (i.e., 800 – 1000 °C).

Metallization also played a role in determining what substrates were used in this work. Initially, the diodes were to be fabricated on single crystal quartz and fused silica substrates for RF testing purposes. However, repeated attempts at metal deposition of a marker layer resulted in poor adhesion to the quartz surface, most likely due to surface contamination on the wafers. While investigating this contamination issue, it was decided to use high resistivity silicon substrate (resistance greater than 10 kΩ/cm) with a thermal oxide layer grown as an alternative. This choice of substrate produced better adhesion while still providing a suitable substrate for RF testing.

The carbon nanotubes were grown on high resistivity silicon with a 5000 Å SiO₂ layer via chemical vapor deposition (CVD). A solution of ferric nitrate dissolved in isopropanol (60 µg/mL) was used as the catalyst. Growth was performed in a quartz tube at 875 °C with a flow of hydrogen, methane, and ethylene gasses for 20 minute after a 45 minute anneal at 875 °C in argon. Using this catalyst method and growth conditions, carbon nanotubes are sporadically

distributed across the substrate. Tube growth and densities were verified using scanning electron microscopy (SEM).

Controlling the growth of nanotubes on the substrate is critical for electronic circuit design. It is preferable to know both the location and number of nanotubes in a device to predict electrical parameters such as characteristic impedance. In order to limit the nanotubes to the desired location between the two metal contacts, a procedure, using oxygen plasma etch which has been shown to remove carbon nanotubes grown by CVD (7), was developed to remove the unwanted nanotubes. A layer of photoresist was spun onto the substrates, and using the image reversal photolithography technique¹, squares were patterned to protect the predetermined sites of the metal-nanotube interfaces. An oxygen plasma etch (power: 200 W, O₂ flow: 20 sccm, time: 2 minutes) was performed on the substrate to clear all extraneous nanotubes not covered by photoresist. After the plasma treatment, the photoresist was dissolved with acetone, leaving only the protected tubes behind. Figure 2 shows a region of the substrate which was protected by photoresist in contrast to the surrounding area which was not covered in photoresist during the oxygen plasma etch.

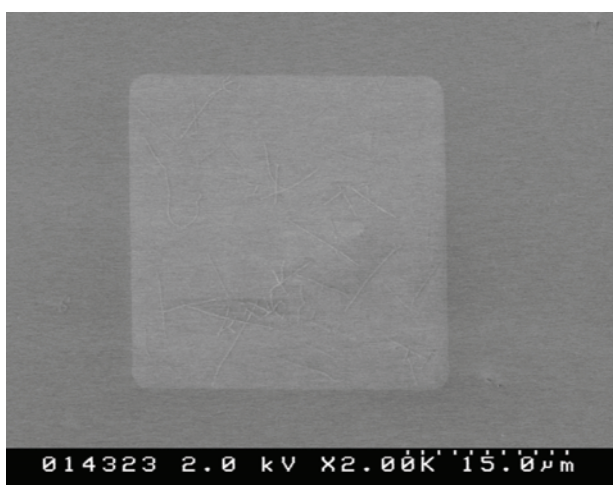


Figure 2. SEM image of photoresist protected tubes after the photoresist was dissolved.

Metallization of the electrodes was a crucial step in fabricating the diodes and required special processing to ensure success. Using standard photolithography processing resulted in poor lift-off, most likely due to slight photoresist overdeveloping. Overdeveloping leads to an angled photoresist profile instead of an abrupt vertical sidewall. This angled profile leads to metal “flashing” along the electrode. An example of this electrode profile can be seen in figure 3. Lift-off resist (LOR), a special resist material, was used in conjunction with AZ 5214E photoresist in order to produce well defined electrode edges and therefore a more reliable lift-off

¹The image reversal process consists of spinning a special positive photoresist, AZ 5214E, which when processed under specific conditions acts as a negative photoresist. The overall result is a negative image of the mask pattern.

process. Metal liftoff was performed using MicroChem Remover PG, a special LOR stripping chemical, at 60 °C. The distribution of the carbon nanotubes between contacts was determined by SEM.

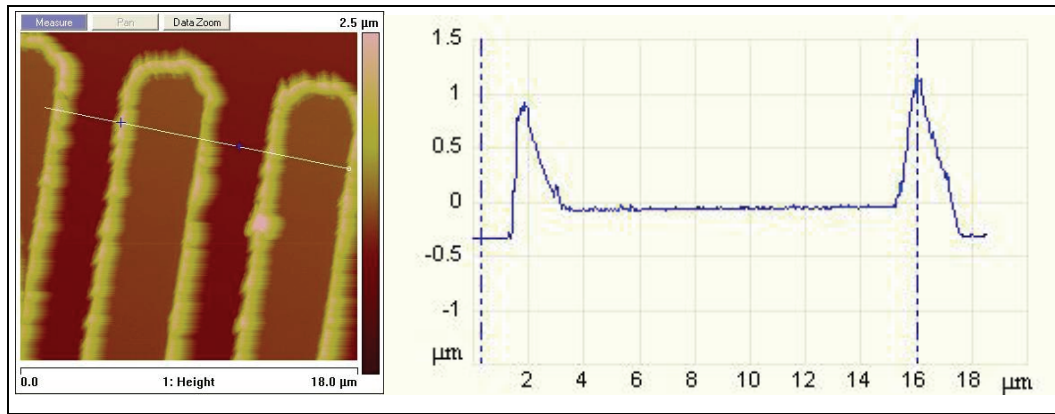


Figure 3. AFM images of metal contacts fabricated using standard photolithography showing the pronounced flashing at the edges.

Diode metallization required the use of two separate masks. The two contact metals chosen were palladium (Pd) and aluminum (Al) for the ohmic and the Schottky contacts respectively because of their work functions with respect to carbon nanotubes. SWNTs have a work function of approximately 4.9 eV, whereas Pd has a value of 5.12 eV and Al has a value of 4.27 eV (6). The metal thicknesses used for the contacts were 80 nm for Al and 20 nm for Pd with a 100 nm layer of Au on top for more robust contacts. Figure 4a shows the diagram of the electrodes, and figure 4b shows an actual SEM image of the fabricated electrodes. Figure 4c shows a schematic picture of the metal-nanotube interface, and figure 4d shows the metal-CNT interface of one of the fabricated devices.

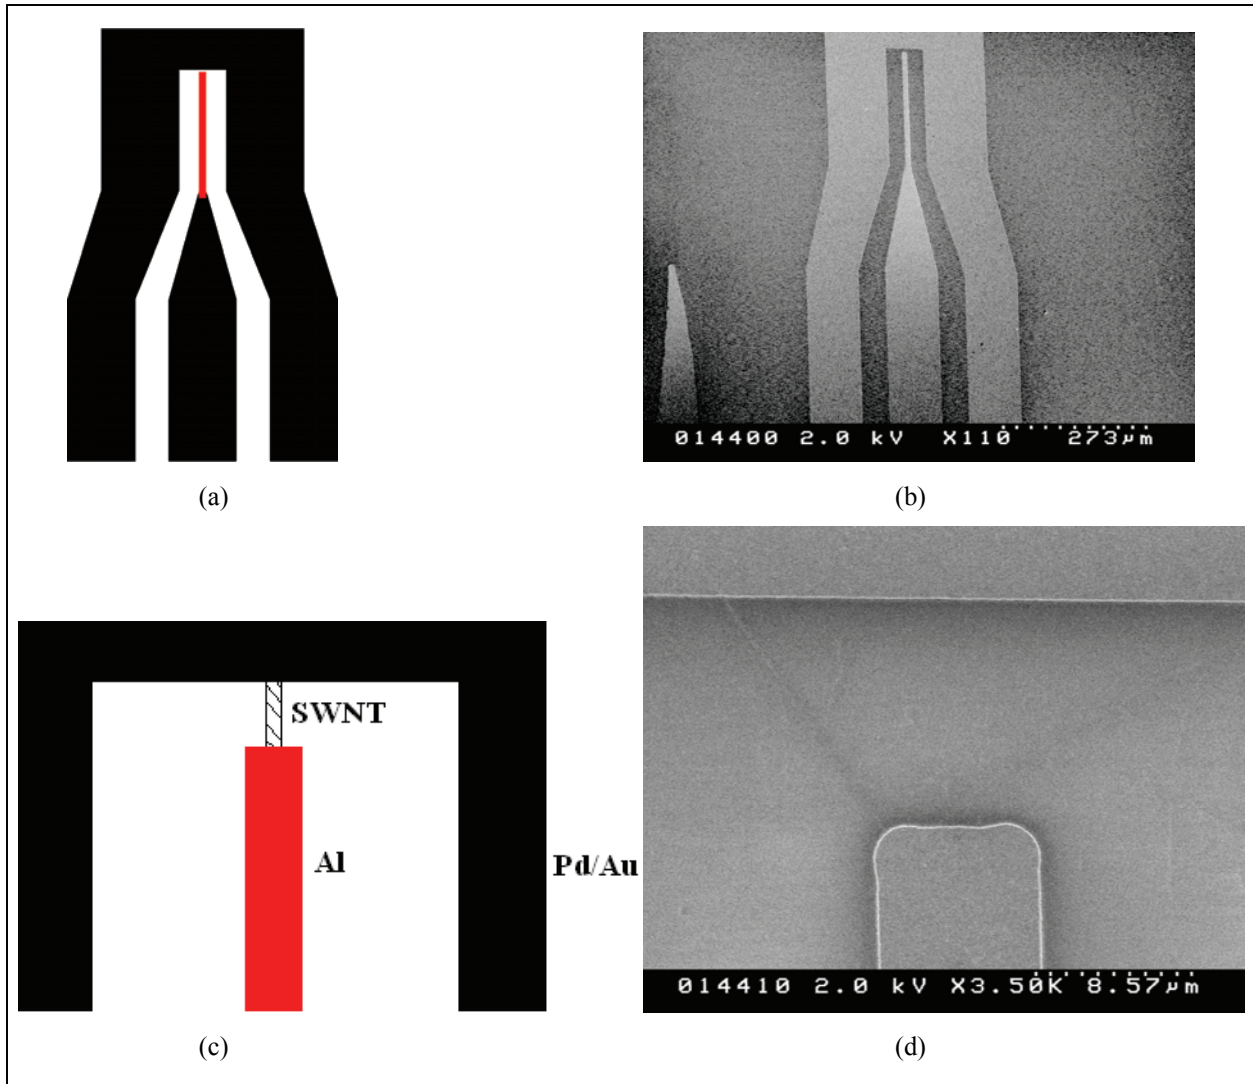


Figure 4. (a) Diode layout: The inner electrode represents the signal electrode (red – Al). The outer electrodes represent the ground electrodes (black – Pd/Au), (b) SEM image of the diode layout, (c) Schematic picture of device setup, and (d) SEM image of electrode-nanotube interface (top contact: Pd/Au, bottom contact: Al).

3. Electrical Testing

The electrode was designed in a coplanar waveguide topology (CPW) for 150 μm pitch probes. CPW was chosen because of its high frequency response as well as its measurement precision and repeatability. Due to the relatively unknown RF characteristics of carbon nanotubes, especially in the GHz frequency range (8), as well as the inability to predict the number and individual characteristics of nanotubes in a device, the electrodes were tapered in an attempt to provide usable impedance matching. High contact resistances are typical in metal-nanotube interfaces, and the number of nanotubes in a device affects its impedance. These conditions

provide significant challenges for electrode design. Developmental work in AC characterization of SWNTs as well as in controlled growth is still required to obtain proper impedance matching in such a device (9).

Devices were tested (at DC) using a Keithley 4200 semiconductor characterization system. All measurements were taken at room temperature in air. The signal pad and one of the ground pads were probed in order to test the nanotubes bridging the Al and Pd electrodes. Rectification was verified by sweeping the voltage across the device from -2 to 5 V.

The mask layout contains 64 diodes per sample with varying gap lengths ranging from 5 to $20\text{ }\mu\text{m}$. Two samples were processed for testing. During electrical testing, 5 useable devices were identified. Figure 5 shows the forward and reverse characteristics for one of these devices. The turn on voltage for this device occurs at 1.1 V.

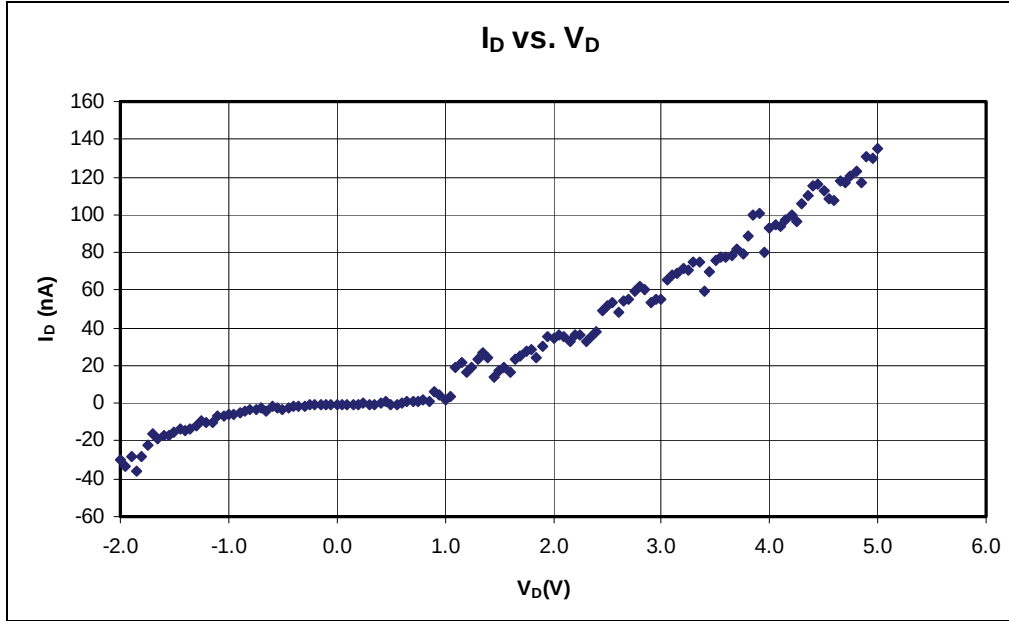


Figure 5. Diode DC I-V curve showing both the forward characteristic and reverse breakdown. The turn on voltage for the device occurs at 1.1 V. The ideality factor for this device is 1.80 .

This behavior was then compared to the characteristic equation governing diode behavior, as seen in equation 1. The equation describes the drain current, I_D , through the diode with respect to the voltage across it, where I_S is the saturation current, n is the ideality factor, and V_T is the thermal voltage. The results were then benchmarked by calculating the ideality factor n for the tested diodes. A value of 1 for n represents an ideal diode, and n generally falls between 1 and 2 for functional diodes. Under low bias, up to 500 mV, ideality factors for the diodes averaged 1.80 .

$$I_D = I_S \left[\exp\left(\frac{V_D}{nV_T}\right) - 1 \right] \quad (1)$$

The results presented here are similar to other CNT diode properties previously reported, but with some differences. These ideality factors are higher than previously achieved values for in-house fabricated diodes using Au and Al contacts, which showed values between $n = 1.1$ to 1.2 (10). When compared to previous devices fabricated using the same contact metallization (Al/Pd), turn on voltages for the devices in this work were roughly 1 V greater (6). Better yield and further investigation into factors contributing to the formation of the Schottky barrier is needed in order to better compare the results conclusively. As our process is optimized and reproducibility increases, it is suspected that these issues will be better understood.

4. Discussion

At this stage of RF diode design development, efforts should be focused to increase yield in order to provide a sufficient sample size to adequately characterize these devices. After yield is increased and device performance is understood, the frequency response of these devices should be explored. It is expected the cutoff frequencies could extend well into the GHz regime due to the high mobilities reported for SWNTs (9).

In addition to cutoff frequency, power transmission in these diodes should also be analyzed. Power transmission measurements, such as RF to DC power conversion efficiency, could give valuable insight into the RF response of the devices as well as the current electrode design. As the AC response of SWNTs is better understood, other parameters of the diode such as input impedance should be defined, and a small signal equivalent circuit model should be developed.

Once these parameters of the devices are determined, these diodes could be used in a variety of applications including detectors, frequency multipliers, and nanoscale rectifying antenna (rectenna) designs. Improved performance at the device level, as is expected by using devices fabricated with multiple SWNTs, will increase the overall performance for these circuit applications.

5. Conclusion

Schottky diodes using single walled carbon nanotubes were fabricated using cleanroom processing techniques and their DC characteristics were tested. The devices fabricated during this research have provided objective evidence of achieving CNT-based Schottky diodes using Pd and Al metal contacts. The fine tuning of these devices will lead to optimization for various applications. Research to determine the optimal conditions required to improve yield, along with the design of suitable device architectures and development of the necessary test environments, are the next step in achieving the potential of carbon nanotube based electronics.

6. References

1. Durkop, T.; Getty, S. A.; Cobas, E.; Fuhrer, M. S. Extraordinary mobility in semiconducting carbon nanotubes. *Nano Letters* **2004**, *4*, 35–39.
2. Wei, B. Q.; Vajtai, R.; Ajayan, P. M. Reliability and current carrying capacity of carbon nanotubes. *Applied Physics Letters* **2001**, *79*, 1172–1174.
3. Chen, Z.; Appenzeller, J.; Knoch, J.; Lin, Y.-M.; Avouris, P. The role of metal-nanotube contact in the performance of carbon nanotube field-effect transistors. *Nano Letters* **2005**, *5*, 1497–1502.
4. Leonard, F.; Tersoff, J. Role of Fermi-level pinning in nanotube Schottky diodes. *Physical Review Letters* **2000**, *84*, 4693–4696.
5. Chenguang, L.; Lei, A.; Qiang, F.; Jie, L.; Hong, Z.; Murduck, J. Schottky diodes from asymmetric metal-nanotube contacts. *Applied Physics Letters* **2006**, *88*, 133501.
6. Yang, M. H.; Teo, K. B. K.; Milne, W. I.; Hasko, D. G. Carbon nanotube Schottky diode and directionally dependent field-effect transistor using asymmetrical contacts. *Applied Physics Letters* **2005**, *87*, 253116.
7. Jespersen, T. S.; Nygard, J. Probing induced defects in individual carbon nanotubes using electrostatic force microscopy. *Applied Physics A-Materials Science & Processing* **2007**, *88*, 309–313.
8. Gomez-Rojas, L.; Bhattacharyya, S.; Mendoza, E.; Cox, D. C.; Rosolen, J. M.; Silva, S. R. P. RF response of single-walled carbon nanotubes. *Nano Letters* **2007**, *7*, 2672–2675.
9. Manohara, H. M.; Wong, E. W.; Schlecht, E.; Hunt, B. D.; Siegel, P. H. Carbon nanotube Schottky diodes using Ti-Schottky and Pt-Ohmic contacts for high frequency applications. *Nano Letters* **2005**, *5*, 1469–1474.
10. Luquette, B. E.; Nichols, B. M. *Fabrication and Characterization of Schottky Diodes using Single Walled Carbon Nanotubes*; US Army Research Laboratory Summer Technical Report, August 2007.

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
1 ELEC	ADMNSTR DEFNS TECHL INFO CTR ATTN DTIC OCP 8725 JOHN J KINGMAN RD STE 0944 FT BELVOIR VA 22060-6218	1	US GOVERNMENT PRINT OFF DEPOSITORY RECEIVING SECTION ATTN MAIL STOP IDAD J TATE 732 NORTH CAPITOL ST NW WASHINGTON DC 20402
1	DARPA ATTN IXO S WELBY 3701 N FAIRFAX DR ARLINGTON VA 22203-1714	1	US ARMY RSRCH LAB ATTN AMSRD ARL CI OK TP TECHL LIB T LANDFRIED BLDG 4600 ABERDEEN PROVING GROUND MD 21005-5066
1 CD	OFC OF THE SECY OF DEFNS ATTN ODDRE (R&AT) THE PENTAGON WASHINGTON DC 20301-3080	1	DIRECTOR US ARMY RSRCH LAB ATTN AMSRD ARL RO EV W D BACH PO BOX 12211 RESEARCH TRIANGLE PARK NC 27709
1	US ARMY RSRCH DEV AND ENGRG CMND ARMAMENT RSRCH DEV AND ENGRG CTR ARMAMENT ENGRG AND TECHNLGY CTR ATTN AMSRD AAR AEF T J MATTS BLDG 305 ABERDEEN PROVING GROUND MD 21005-5001	4	B LUQUETTE 6 HILLSIDE DR RAYMOND NH 03077
1	US ARMY TRADOC BATTLE LAB INTEGRATION & TECHL DIRCTRT ATTN ATCD B 10 WHISTLER LANE FT MONROE VA 23651-5850	16	US ARMY RSRCH LAB ATTN AMSRD ARL CI OK T TECHL PUB ATTN AMSRD ARL CI OK TL TECHL LIB ATTN AMSRD ARL SE R P AMIRTHARAJ ATTN AMSRD ARL SE RL B PIEKARSKI ATTN AMSRD ARL SE RL M DUBEY ATTN AMSRD ARL SE RL B NICHOLS (10 COPIES) ATTN IMNE ALC IMS MAIL & RECORDS MGMT ADELPHI MD 20783-1197
1	PM TIMS, PROFILER (MMS-P) AN/TMQ-52 ATTN B GRIFFIES BUILDING 563 FT MONMOUTH NJ 07703		
1	US ARMY INFO SYS ENGRG CMND ATTN AMSEL IE TD F JENIA FT HUACHUCA AZ 85613-5300		
1	COMMANDER US ARMY RDECOM ATTN AMSRD AMR W C MCCORKLE 5400 FOWLER RD REDSTONE ARSENAL AL 35898-5000		
		TOTAL: 31 (29 HCS, 1 CD, 1 ELEC)	