

# **Nano-Thermoelectric Devices Fabricated by Ion Beam Writing**


**M. K. Wu**

**Institute of Physics, Academia Sinica  
Nankang, Taipei, Taiwan**

**Collaborators**

**M. N. Ou, P. C. Lee, C. T. Chen, and Y. Y. Chen**

**Nanomaterial and Low Temperature Physics Laboratory  
Institute of Physics, Academia Sinica**

The background of the slide features several faint, concentric circular patterns in a lighter shade of blue, resembling ripples on water or a target pattern, positioned in the lower right and bottom center areas.

## Report Documentation Page

*Form Approved*  
*OMB No. 0704-0188*

Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

1. REPORT DATE <b>24 SEP 2007</b>		2. REPORT TYPE <b>FInal</b>		3. DATES COVERED <b>01-12-2007 to 01-12-2008</b>	
4. TITLE AND SUBTITLE <b>Nano-Thermoelectric Devices Fabricated by Ion Beam Writing</b>				5a. CONTRACT NUMBER <b>FA48690714028</b>	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) <b>Maw Kuen Wu</b>				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) <b>Academia Sinica,128 Academia Rd., Section 2,Nankang, Taipei 11529,TW,11529</b>				8. PERFORMING ORGANIZATION REPORT NUMBER <b>N/A</b>	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) <b>AOARD, UNIT 45002, APO, AP, 96337-5002</b>				10. SPONSOR/MONITOR'S ACRONYM(S) <b>AOARD</b>	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S) <b>AOARD-074028</b>	
12. DISTRIBUTION/AVAILABILITY STATEMENT <b>Approved for public release; distribution unlimited</b>					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT <b>A lithographic process has been developed to construct the suspended structure. The self-heating 3W method and measurement systems for nanoscale material have been constructed. The thermal conductivity and specific heat of diameter of 180nm nickel sires are 23 W/m-K and 64.6 J/mol-K (at 25C), respectively. A 30 nano-wire has been fabricated for concept demonstration.</b>					
15. SUBJECT TERMS <b>Nano-Technology, PowerMEMS, Thermoelectric</b>					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT <b>Same as Report (SAR)</b>	18. NUMBER OF PAGES <b>30</b>	19a. NAME OF RESPONSIBLE PERSON
a. REPORT <b>unclassified</b>	b. ABSTRACT <b>unclassified</b>	c. THIS PAGE <b>unclassified</b>			

# Nanotechnology and Energy

## *Improved efficiency of energy usage:*

- Non-thermal energy usage, via nanostructured devices such as fuel cells;
- Molecularly tailored catalysts, for heightened selectivity and byproduct elimination;
- High-strength materials, which will decrease transportation costs;
- Electricity storage and electrosynthesis, both for portable power sources, and for chemical fuel generation;
- Distributed fabrication, to minimize transportation infrastructure.

## *Information-intensive energy extraction:*

- Extensive real-time sensing, for better conventional resource extraction;
- Cheap nanofabrication, which will make practical distributed collection from diffuse sources, as well as better energy management through such devices as "smart windows" and non-thermal light sources

# Nanotechnology and Energy

## *Solid-state energy generation:*


- Solar power, via photovoltaics and artificial photosynthesis;
- Thermoelectric conversion, the direct solid-state transformation of thermal gradients into electricity;
- Piezoelectric conversion, for direct conversion of mechanical energy into electricity.
- Solid electrolytes—critical in fuel cells and supercapacitors; relevant to intercalation batteries, smart windows, electrocatalysis, and also to ionic separation.

## *Nanoscale structuring at an interface is fundamental to many applications, including:*

- Catalyst surfaces;
- Large-area semiconductor p-n junctions, critical to thermoelectric and photovoltaic materials;
- Nanolayered structures, such as for high-performance capacitors, thermoelectric materials, multijunction photovoltaics, piezoelectric stacks, and sensitized photosynthetic materials.

# Nanotechnology and Energy System

## Energy Source/Materials

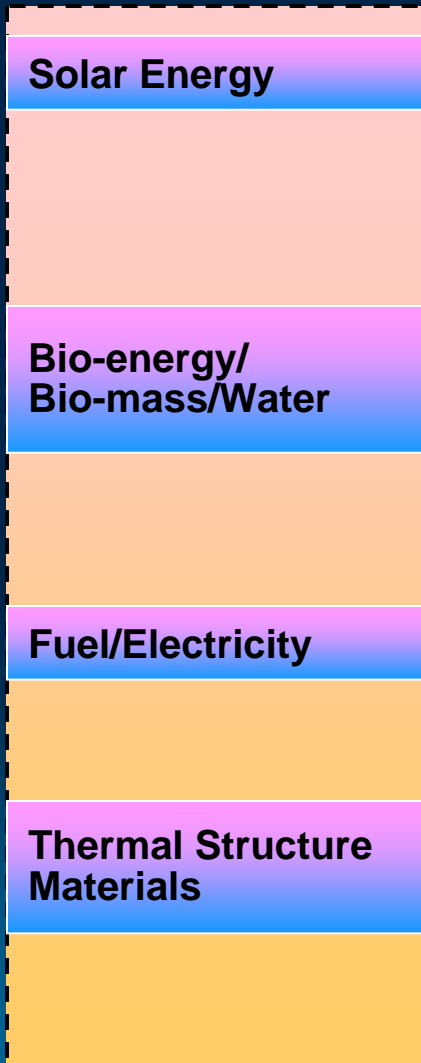

## Critical Nanotechnology


Full spectrum nanomaterials  
Printable /Flexible material  
& substrate  
Nano-scale crystalline  
silicon

Bio-catalyst / Biodegradable  
Chirality centered material  
Functional Nano-fibers

High active Bio-fuel  
Nano Structural Materails for  
catalyst  
Nanostructural  
Organic/Inorganic Materials  
Hyper-branch catalyst  
Organic/Inorganic  
electrolyte

Nanostructure Low  
Phonon scattering, high  
ZT Materials  
Surface Plasmon  
Quantum well design



## System Platform

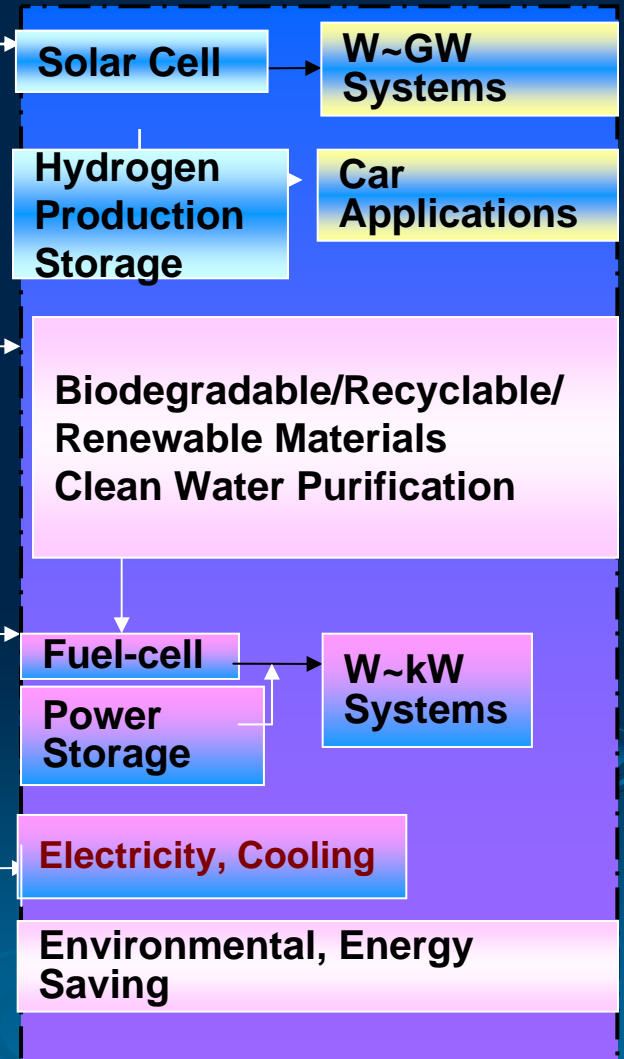

\* **Energy conversion efficiency**    **Figure of Merit  $\square$  ZT**



$$ZT = \frac{\alpha^2 \sigma T}{(\kappa_E + \kappa_L)}$$

$\alpha$  is Seebeck Coefficient.  
 $\sigma$  is Electric Conductivity.  
 $\kappa$  is Thermal Conductivity  
 $T$  absolute temperature

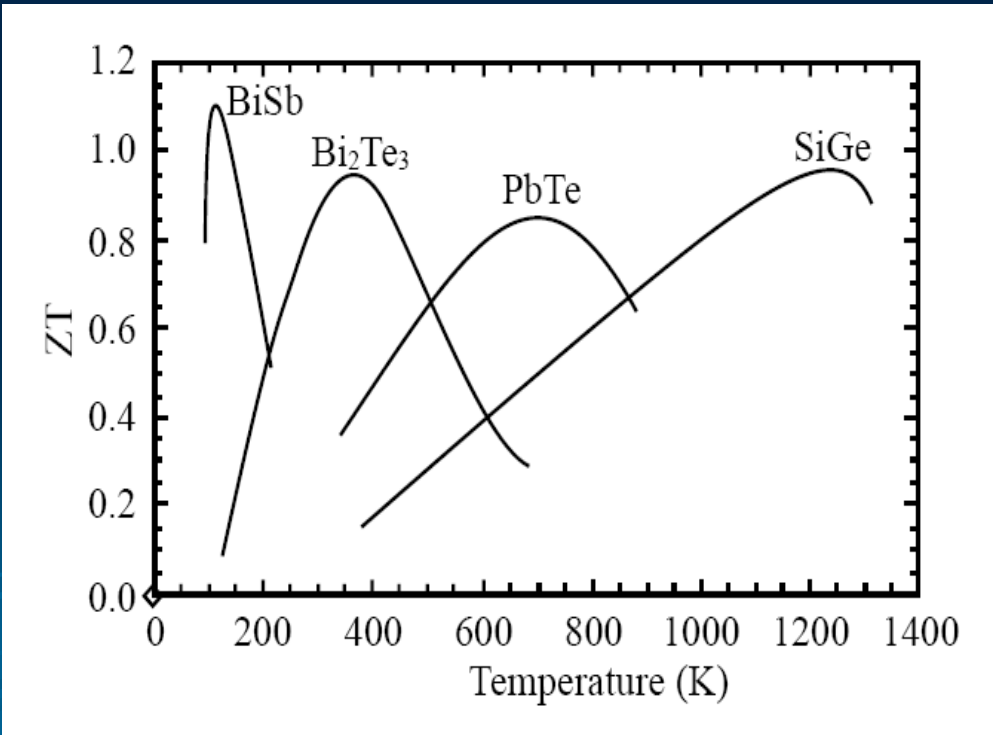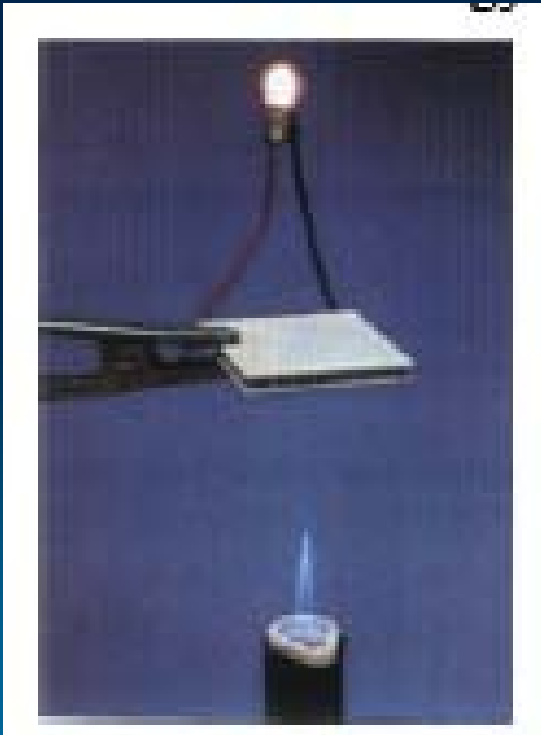

$$ZT = \frac{\alpha^2 \sigma T}{(\kappa_E + \kappa_L)}$$

\* How to increase ZT ?

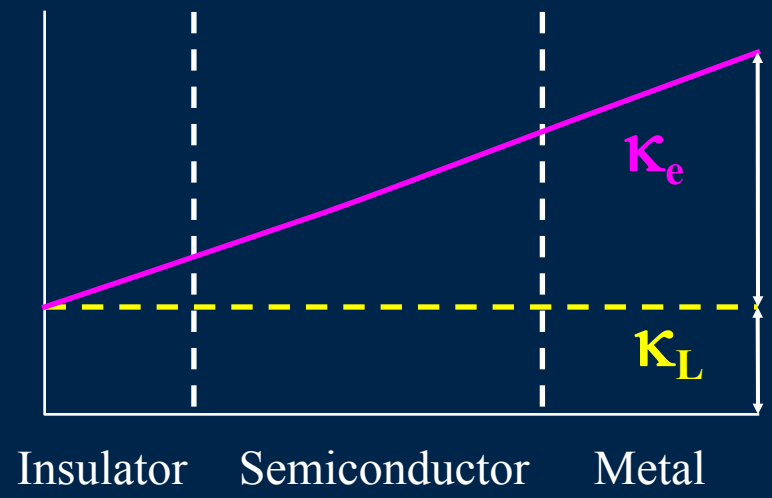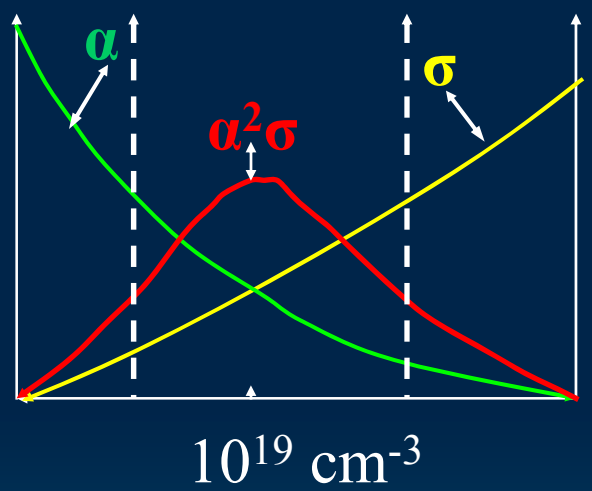

$\alpha, \sigma (D(\epsilon), \epsilon_F, \mu)$

$\sigma / \kappa_e = 1 / (L_0 T)$   
*Wiedmann-Franz Law:*  
 $L_0$  □ Lorentz num.

Reduce phonon thermal conductivity

# Strategy

1. Increase Seebeck Coefficient  $\alpha$   $\square$  quantum size effects,



Example: Quantum Wires in Nanostructures

2. Reduce thermal conductivity  $\kappa_L$   $\square$  decrease lattice phonons mean free path.



Example: Multilayers or Superlattice , Nanostructured bulk materials (nanoparticle-dispersed composites)

3. Directional dependent of thermal conductivity


## (A) Crystal Structures with "Rattlers"

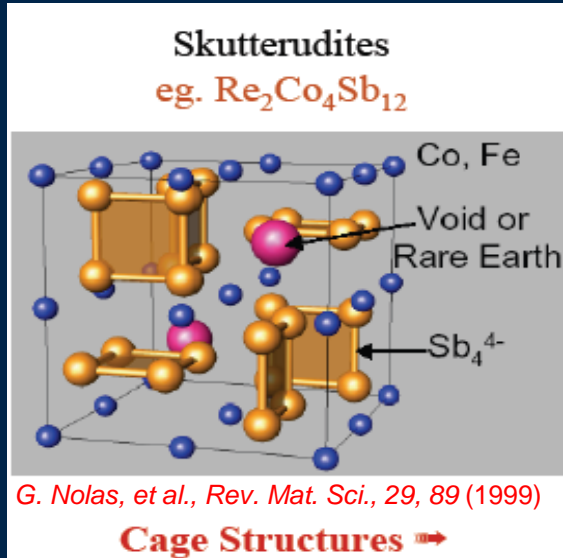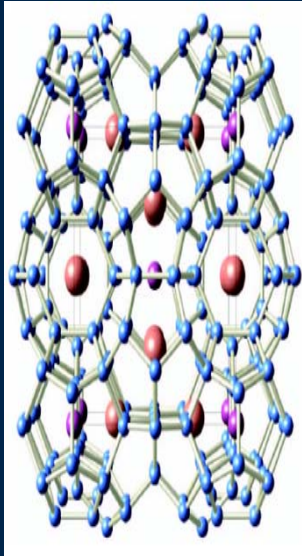

## (B) Superlattice Lattices

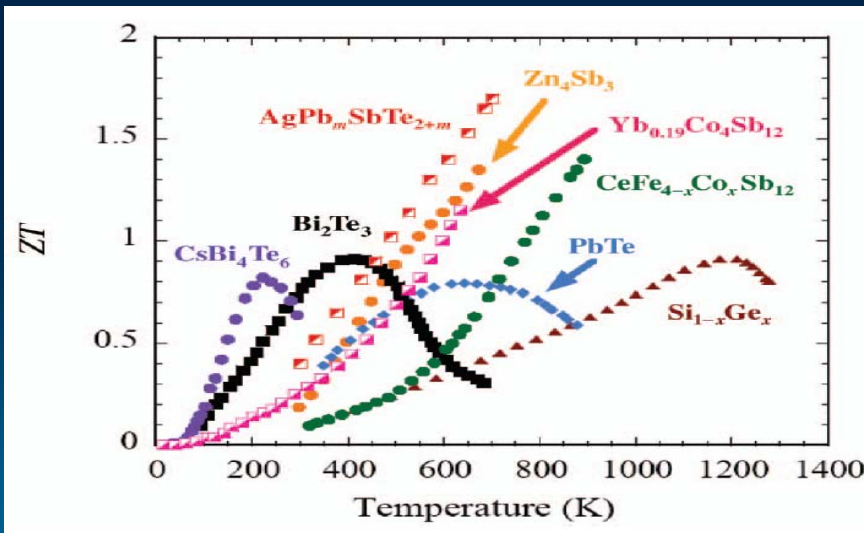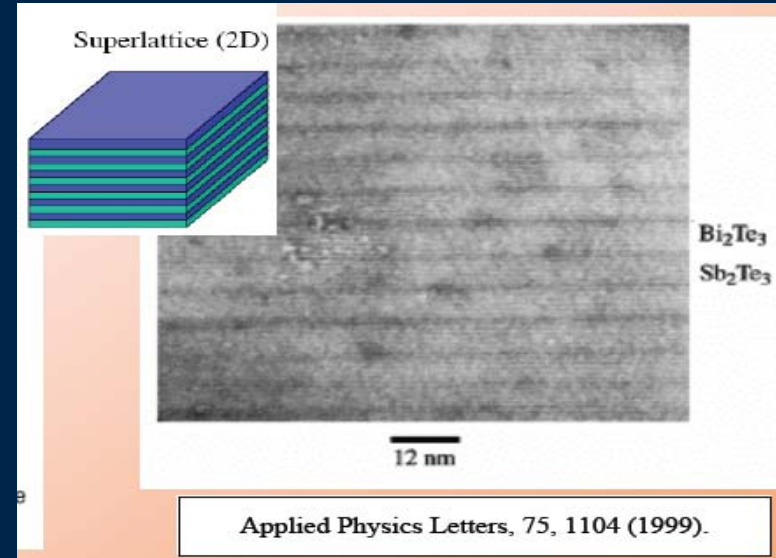


Need higher  $ZT \sim 1.5-2$

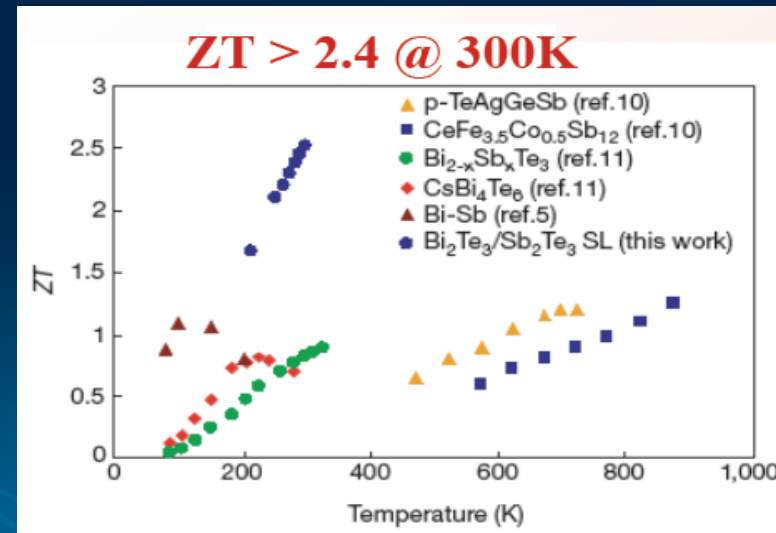


Too thin and too expensive



# Enhancement of ZT in Nanowire Array

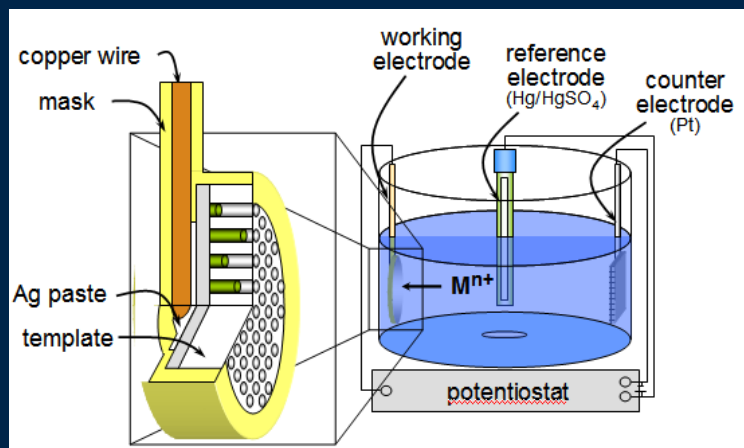


Anodic Aluminum Oxide (AAO)

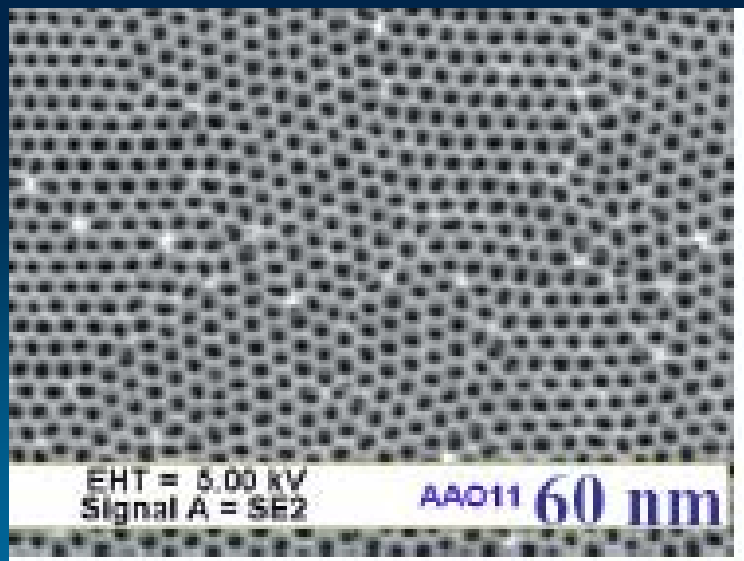


~50 nm Bi<sub>2</sub>Te<sub>3</sub>  
Nanowire array

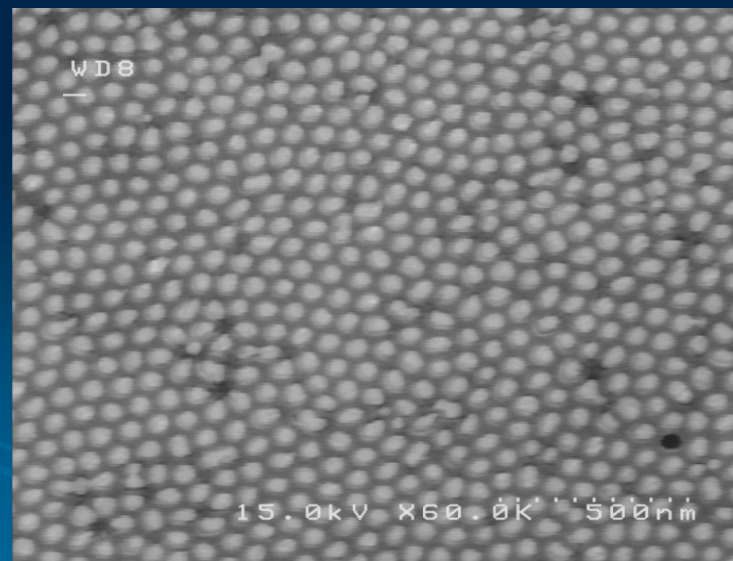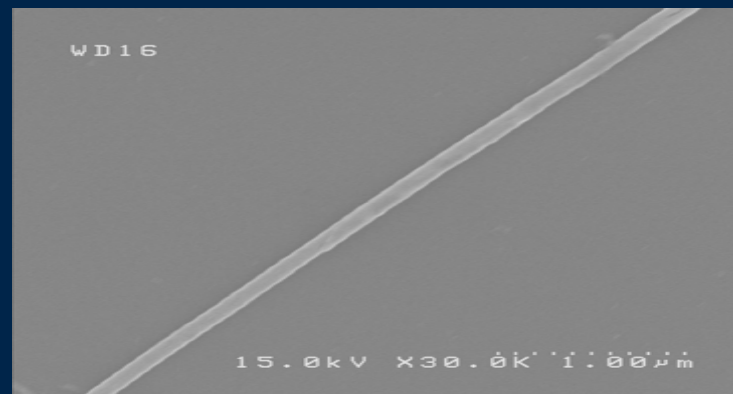

# Thermal Diffusivity of $\text{Bi}_2\text{Te}_3$ Bulk and Nanoarray

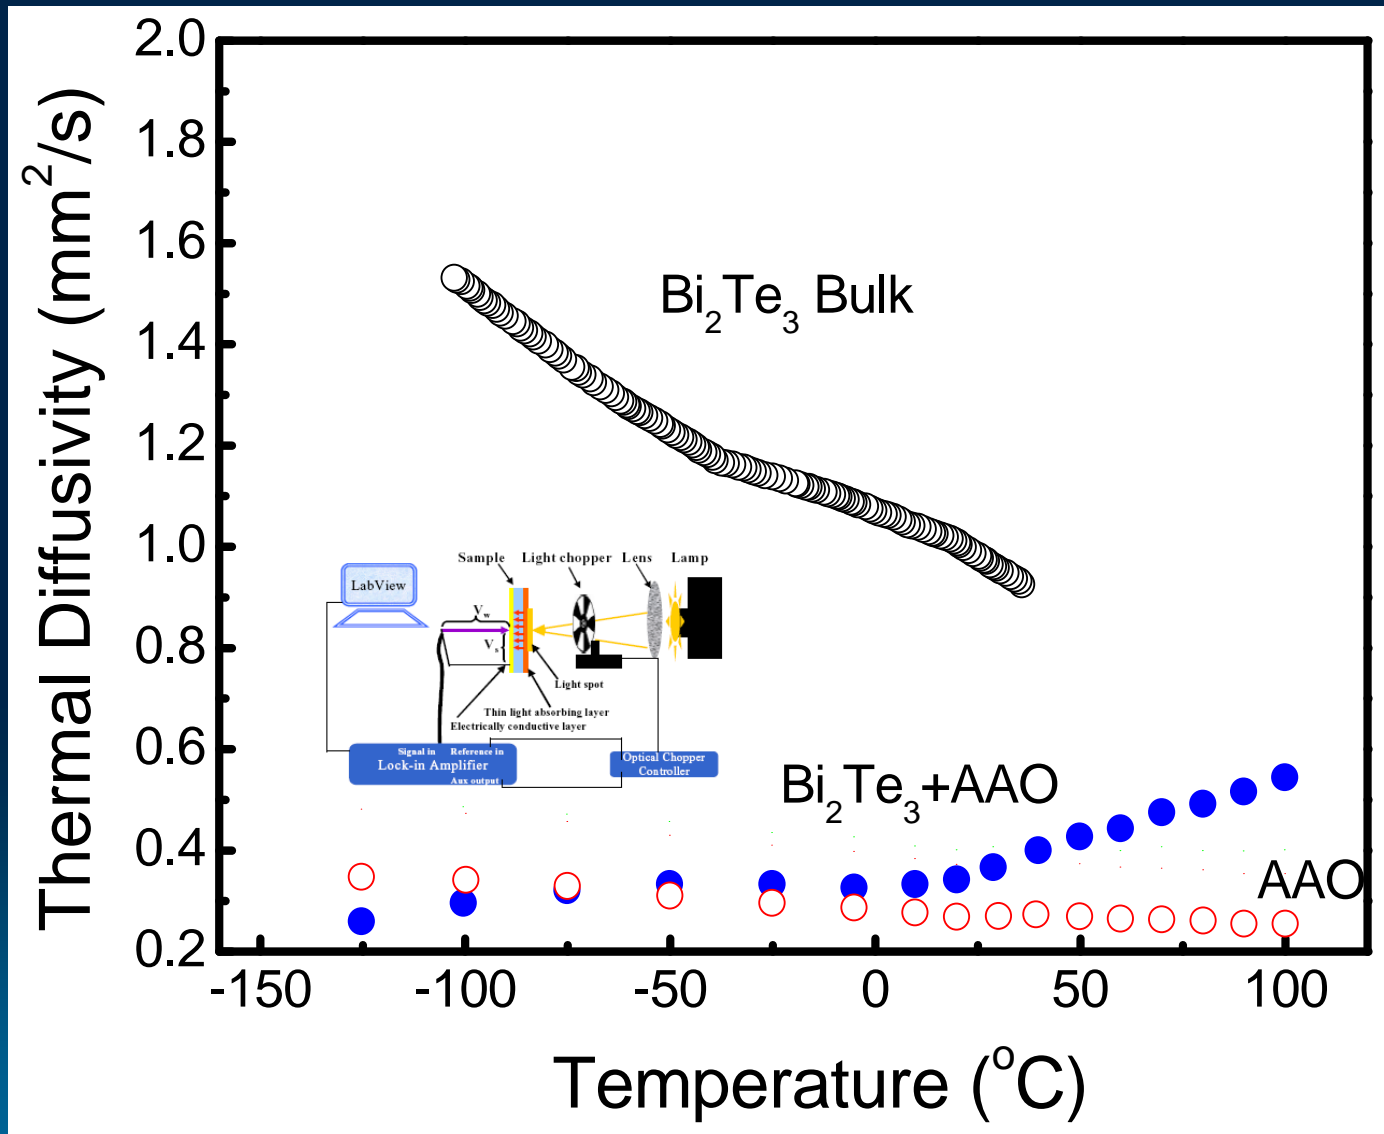

# Resistivity of $\text{Bi}_2\text{Te}_3$ Bulk and Nanowire Array

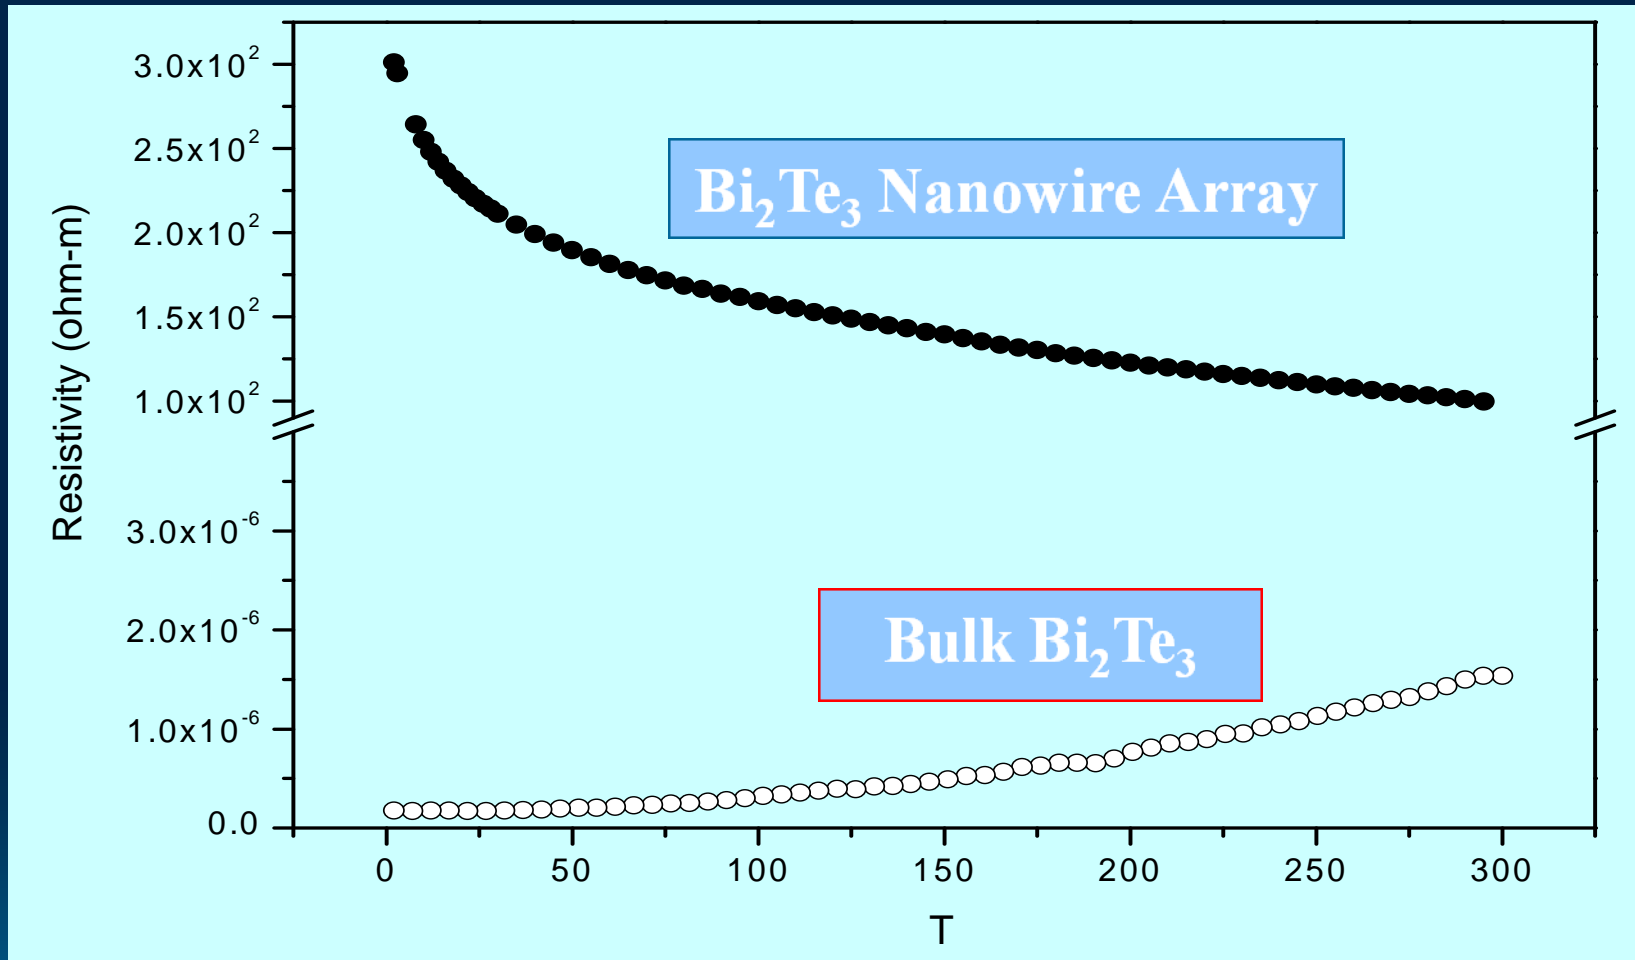

**Need to overcome the large resistivity !!**  
**Better quality sample ?**

# Action Plan

- Nanometer  $\text{Bi}_2\text{Te}_3$  nanowires fabricated by ion-milling creating “neck” diameters close to the mean free path will be examined using the  $3\omega$  process to determine the effect of nanowire diameter on thermal conductivity properties.
- Quantifying the change in heat conduction experimentally in variable diameters provides insight to the theorized mechanisms of thermoelectric performance enhancement and advances designing practical nanothermoelectric devices.
- Experimentally study phonon heat conduction in Ion Milled  $\text{Bi}_2\text{Te}_3$  Nanowires and 2 dimensional tapered structures to investigate significant performance advance attributed to decreasing heat conduction by phonons – without significant alterations of resistance properties.

# Experimental Details—Nanowires


- Fabrication of one individual & suspending nickel nanowire
  - Evaporation deposition
  - E-beam lithography
  - Anisotropic Wet-Etching
- Observation for nano-scale materials
  - $3\omega$  method
    - Electrical conductivity
    - Thermal conductivity
    - Specific heat

# Self heating $3\omega$ Method


- The basic idea of the  $3\omega$  self-heating method is that when one passes an *alternating current* with frequency  $\omega$ , it will heat the wire uniformly.
- If we make a suspension structure, as shown in the next slide, i.e., a uniform wire lies on a high thermal conductive substrate so that the ends part are contacted with substrate but middle part is not.
- It then created a temperature distribution, which with highest temperature rising at mid point and lowest at end point.
- The responded  $1^{\text{st}}$  harmonic signal gives the information of electrical conductivity, and  $3^{\text{rd}}$  harmonic term the temperature variation.
- Thus, parameter  $\kappa$  and specific heat  $C_p$  can be determined by fitting the signal of  $3\omega$  voltage with the formula.

# Idea of self heating $3\omega$ Method

$$\rho C_p \frac{\partial}{\partial t} T(x,t) - \kappa \frac{\partial^2}{\partial x^2} T(x,t) = \frac{I_0^2 \sin^2 \omega t}{LS} (R + R'(T(x,t))) - T_0$$

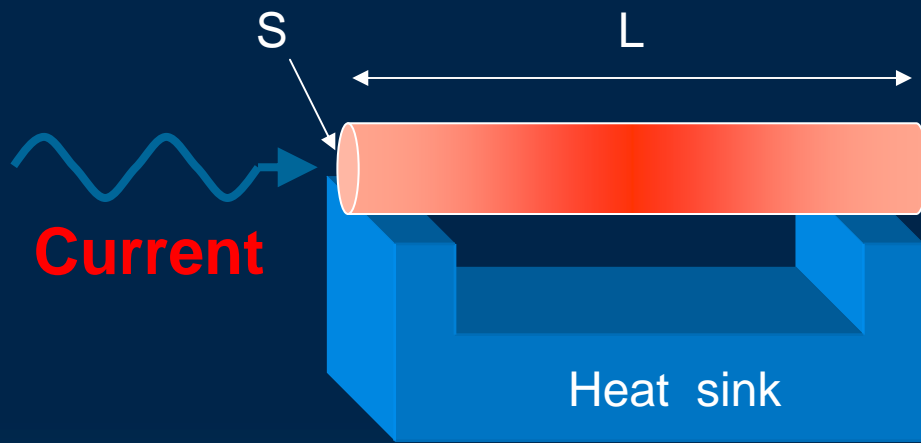

- $\rho$  □ density
- $C_p$  □ specific heat
- $\kappa$  □ thermal conductivity
- $L, S$  □ dimension of specimen
- $R$  □ Resistance
- $\gamma$  □ time constant

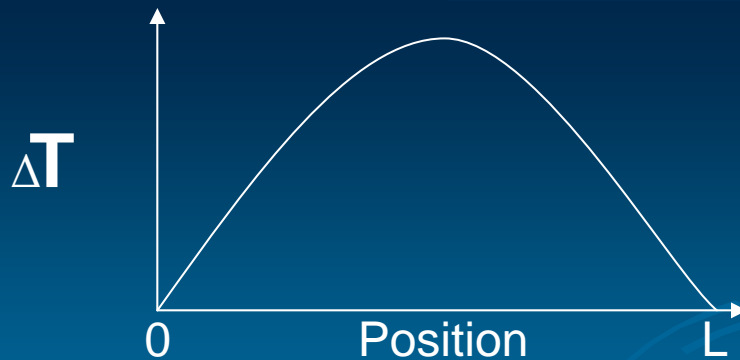



$$V_{3\omega}(t) \approx - \frac{2I_0^3 L R R'}{\pi^4 \kappa S \sqrt{1 + (2\omega\gamma)^2}} \sin(3\omega t - \phi),$$

$$C_p = \pi^2 \gamma \kappa / \rho L^2$$

# 3 $\omega$ Method

- To construct a measurement system of thermodynamic parameters for nanoscale specimen.

1. *Suspended*
2. *Highly thermal conductive to heat sink*
3. *minimize the heat loss*


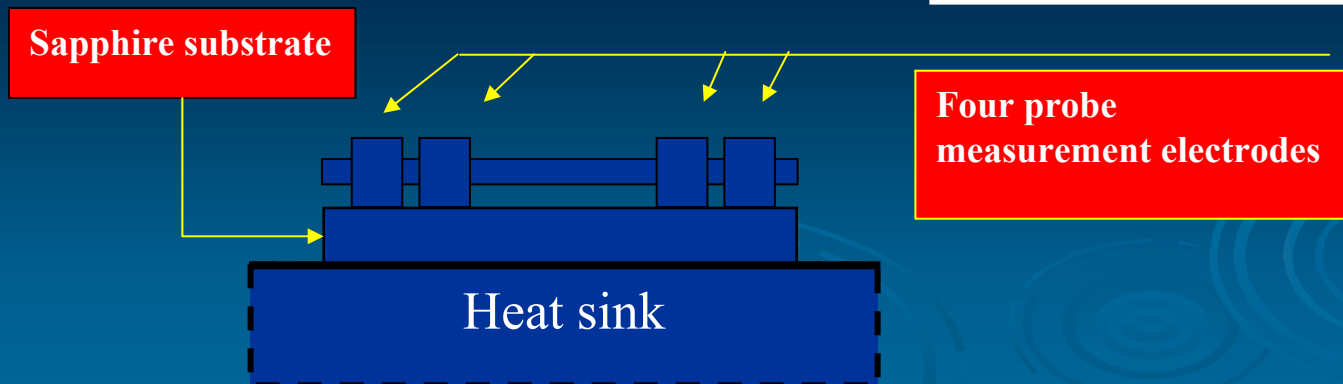
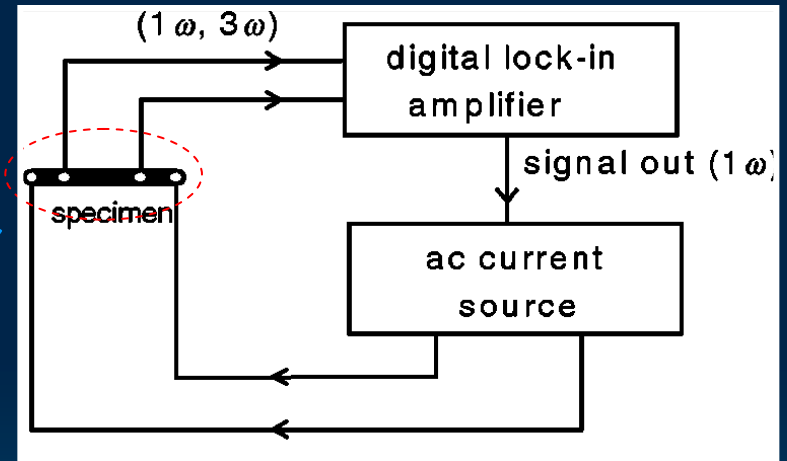


# Fabrication of Individual Nanowire—Nickel




E-beam lithography & evaporate deposition





# E-beam Lithography (EBL)

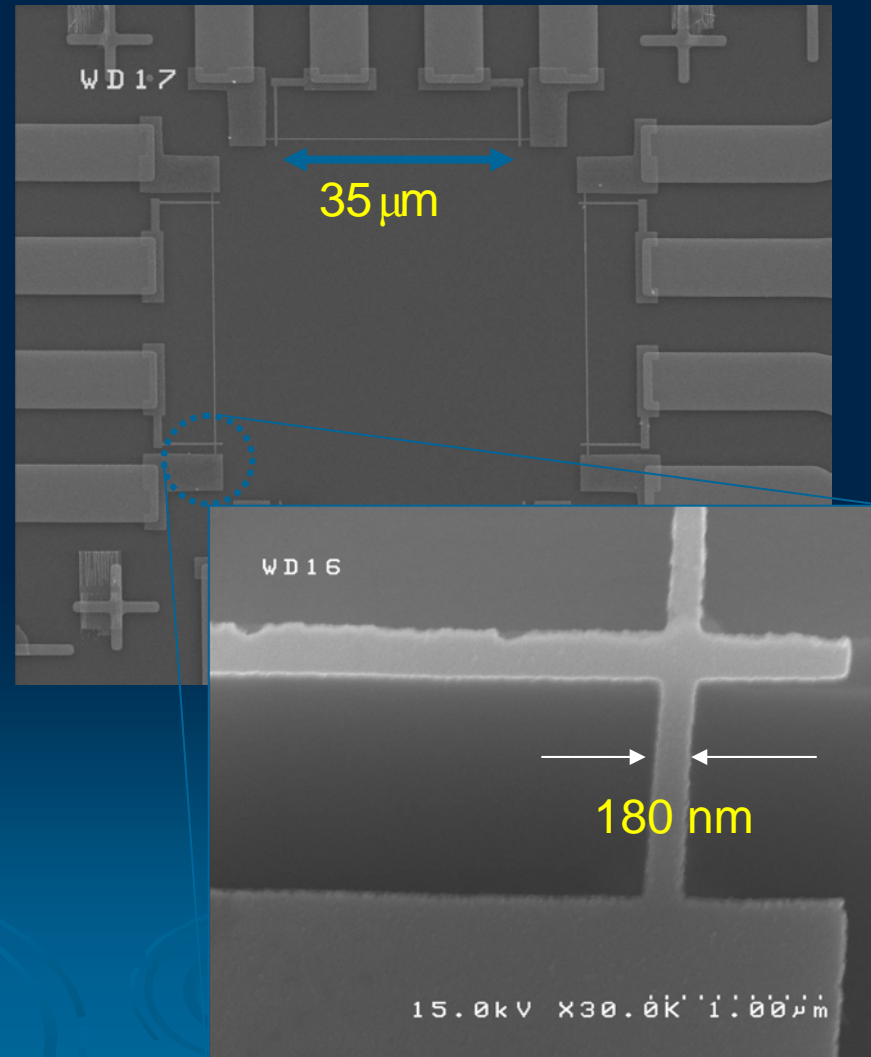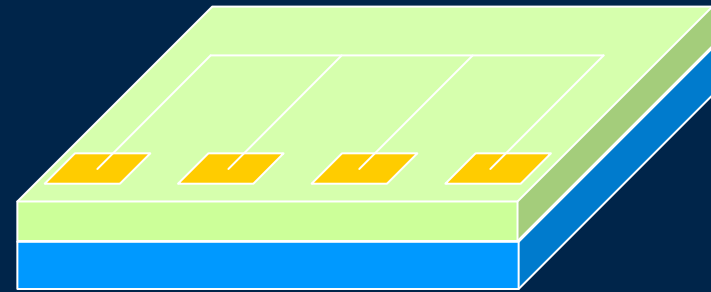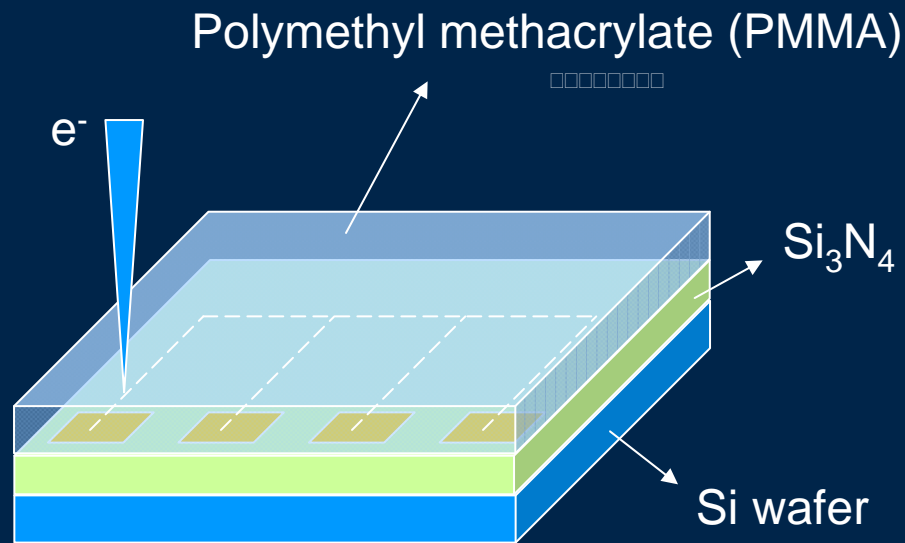


# Dry Etching

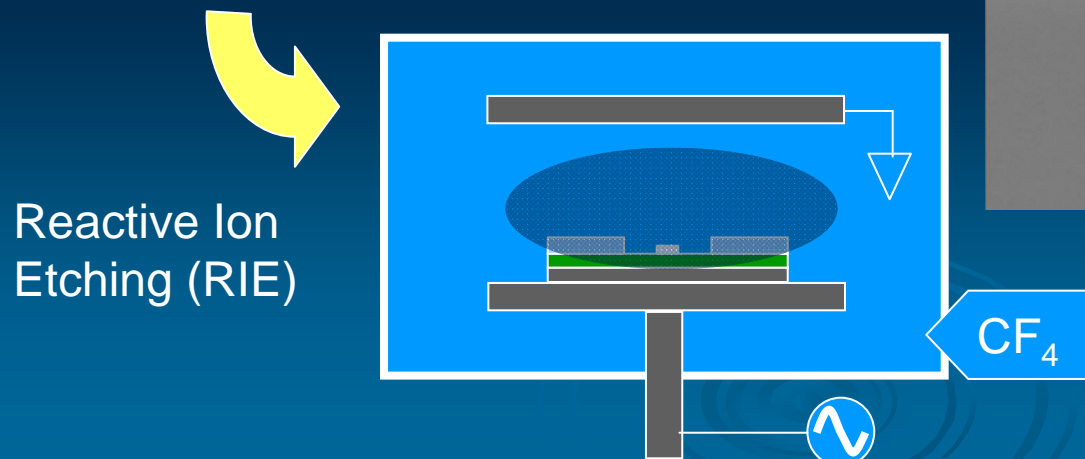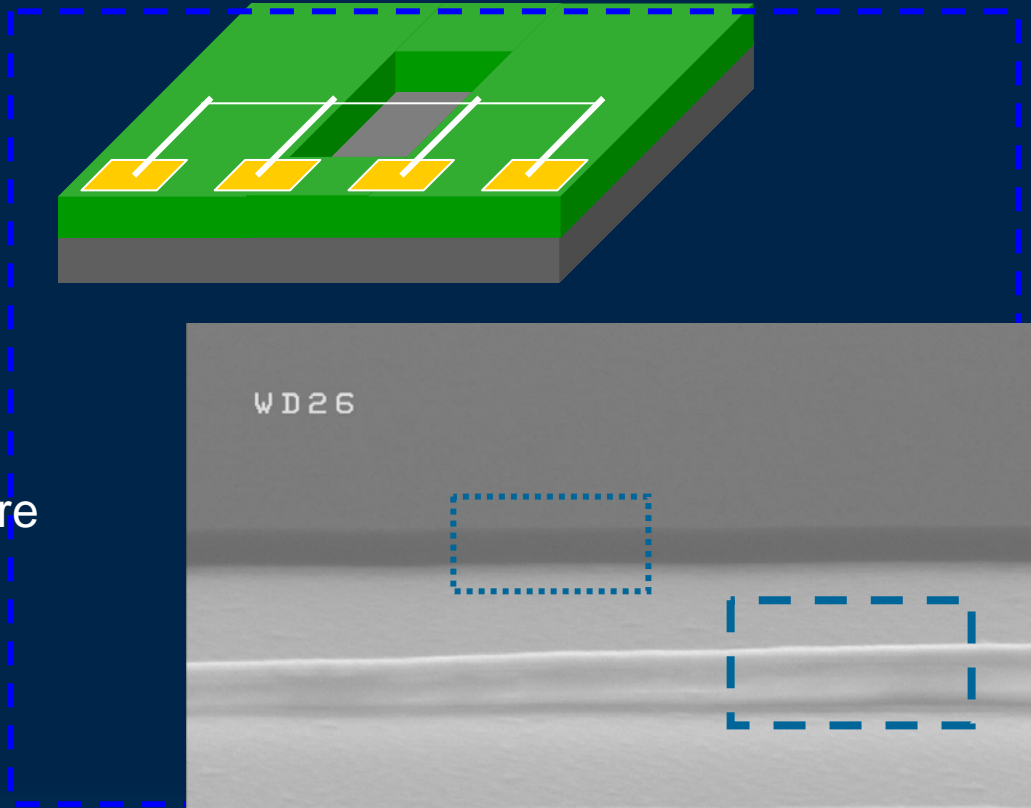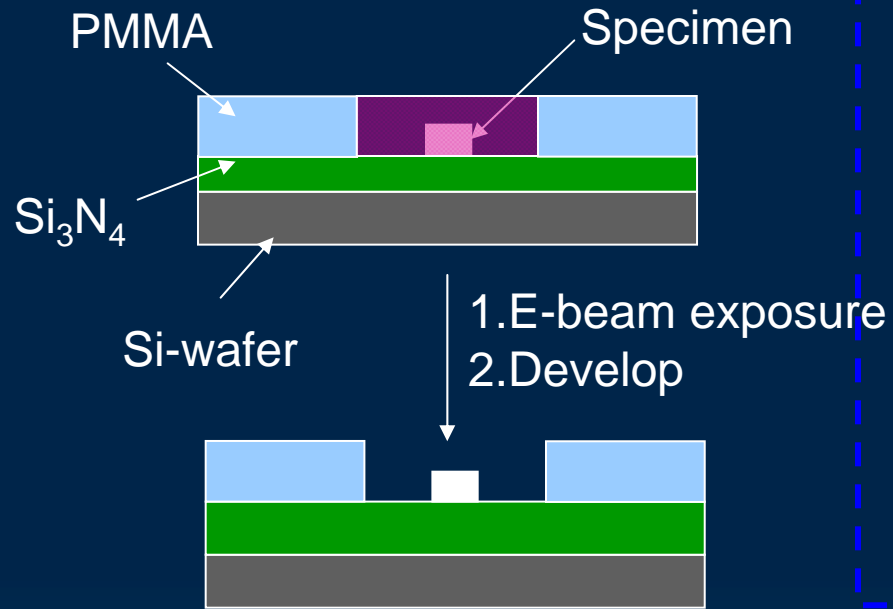

# Wet Etching

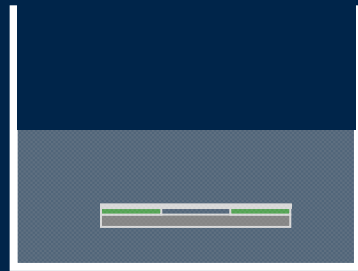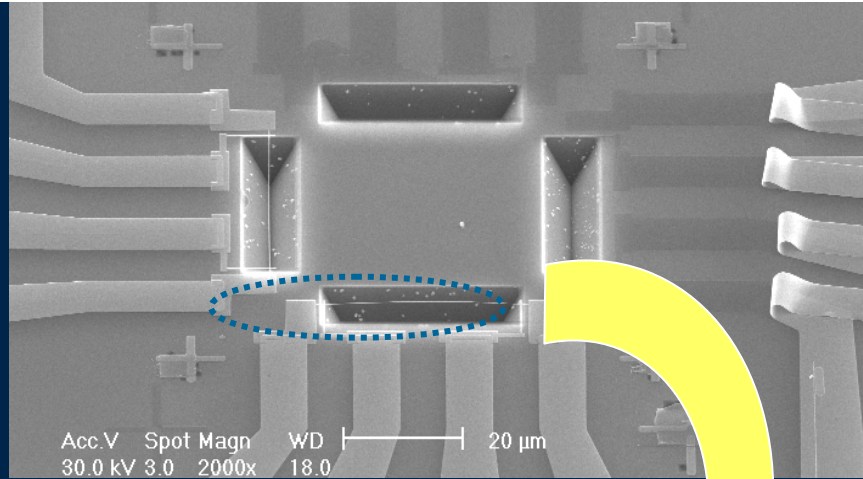


KOH  
Wet etching

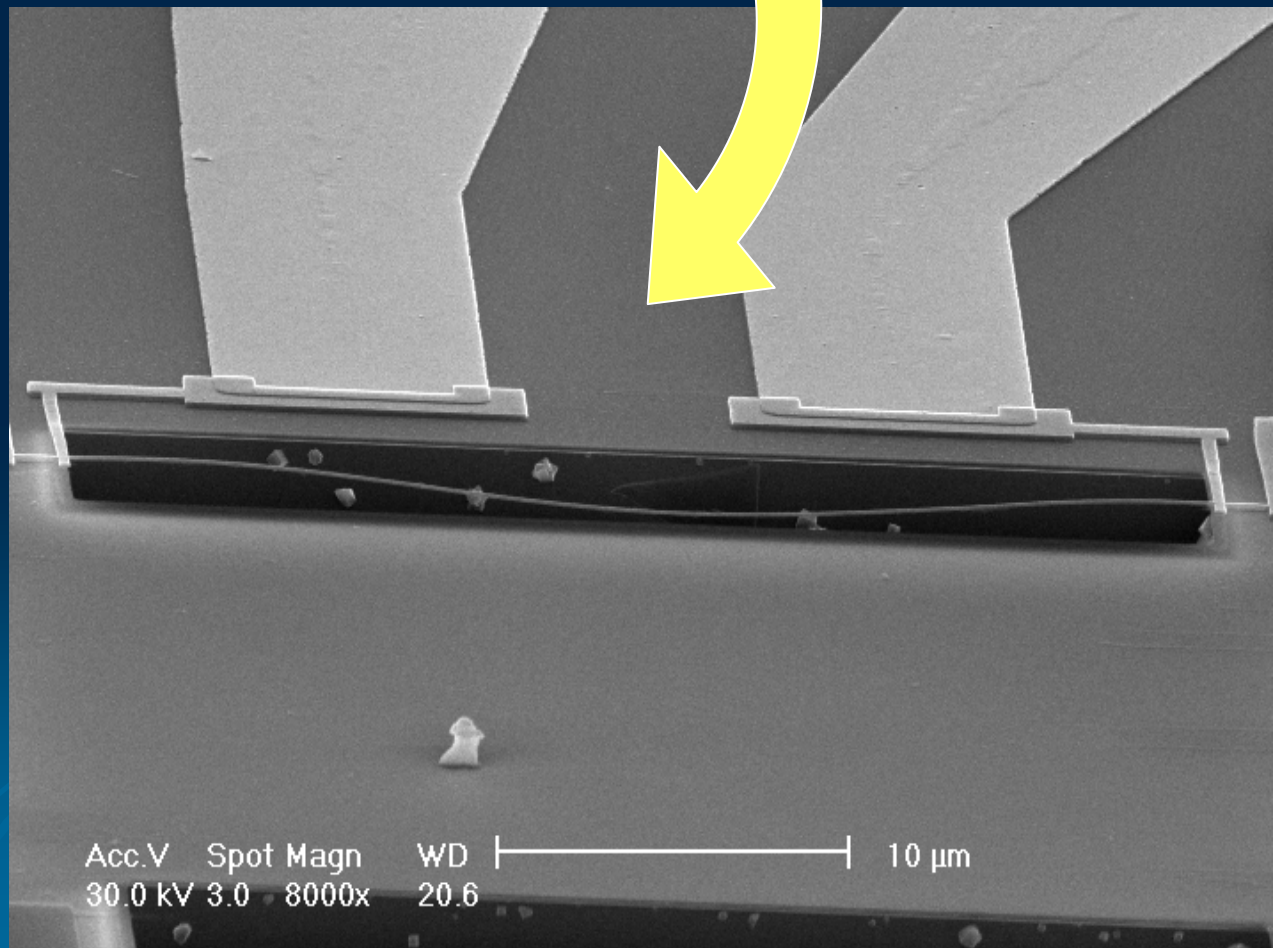

# Method for single nanowire

## Three requirements


1. *Suspended*
2. *Highly thermal conductive to heat sink*
3. *Minimize the heat loss*

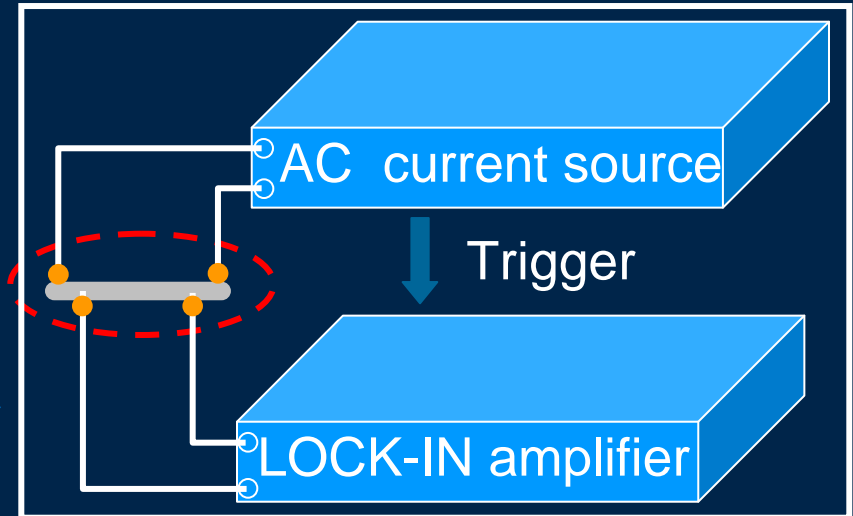


**Four-probe measurement electrodes**

**Sapphire, Si wafer**

**Heat sink**

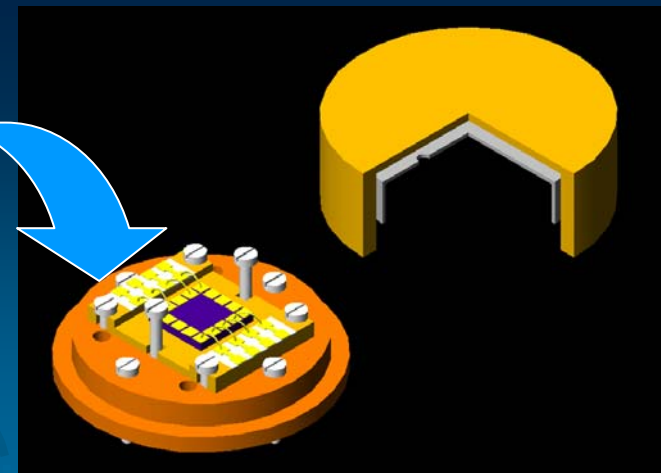

# Electrical Resistivity

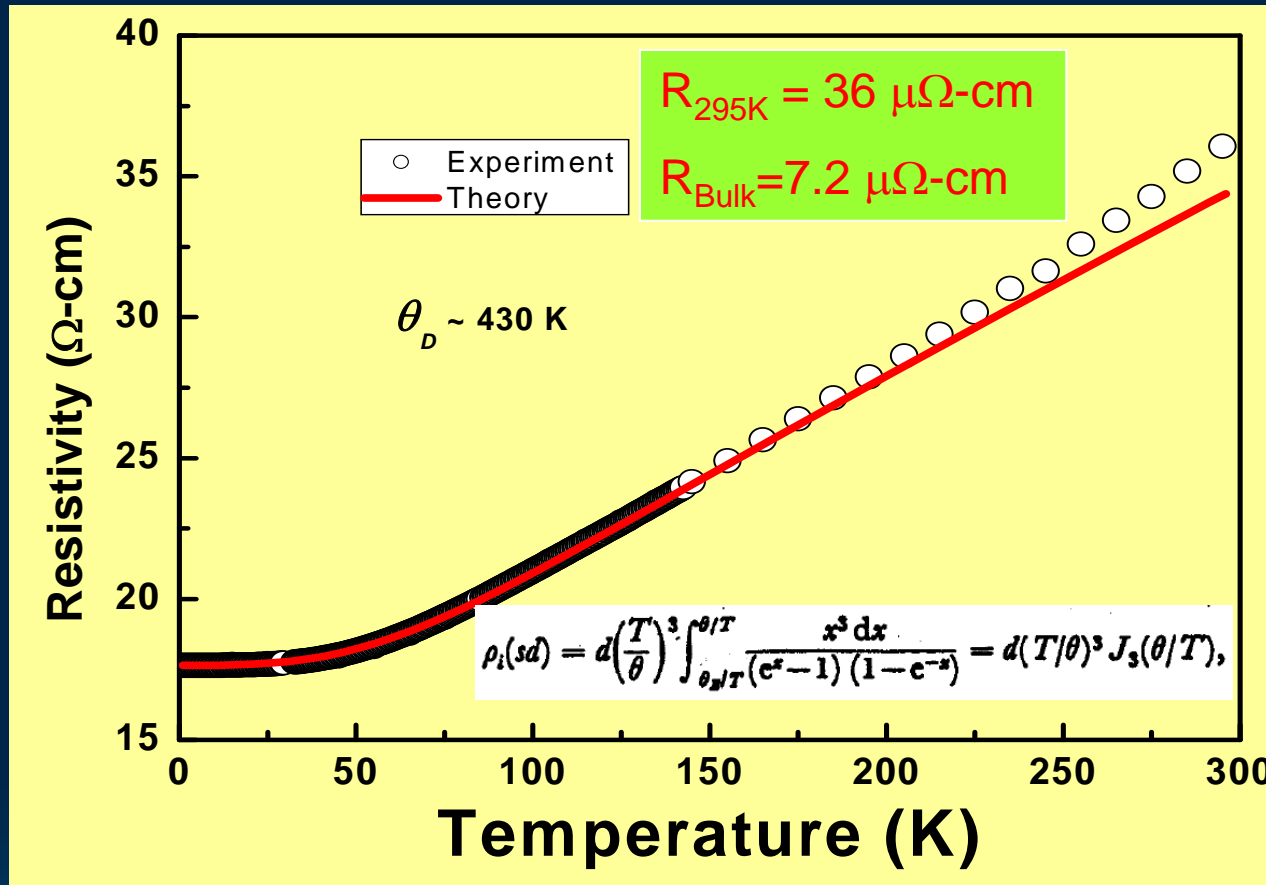

## Relative Resistance Ratio


$$RRR_{295-15} \square 2.04$$


$$RRR_{\text{pure}} \square 47.4$$

TABLE 5. PHYSICAL DATA

element	structure	$M$	$\theta_D$ ( $^{\circ}\text{K}$ )	$\frac{\rho M \theta_D^3}{T}$	$\lambda_{295}$ (expt.) ( $\text{W cm}^{-1}$ $\text{deg}^{-1}$ )	' $\lambda_{295}$ ' $= L T / \rho$	$\gamma$ ( $10^{-3} \text{ J/}$ $\text{mole deg}^2$ )
Fe	b.c.c.	55.85	400	0.7‡	0.82	0.73 <sub>8</sub>	5.0
Ru	h.c.p.	101.7	500	1.5	—	0.98 <sub>1</sub>	3.3
Os	h.c.p.	190.2	400	2.2	—	0.79 <sub>2</sub>	2.3
Co	h.c.p.	58.9	380	0.3 <sub>5</sub> ‡	—	1.25	5.0
Rh	f.c.c.	102.9	350	0.5	1.51	1.51	4.9
Ir	f.c.c.	193.1	290	0.65	1.46	1.43	3.1
Ni	f.c.c.	58.7	390	0.45‡	0.91	1.03	7.0
Pd	f.c.c.	106.7	295	0.8	0.7	0.68 <sub>5</sub>	9.9
Pt	f.c.c.	195.2	225	0.8	0.7	0.69	6.7

# Thermal Conductivity

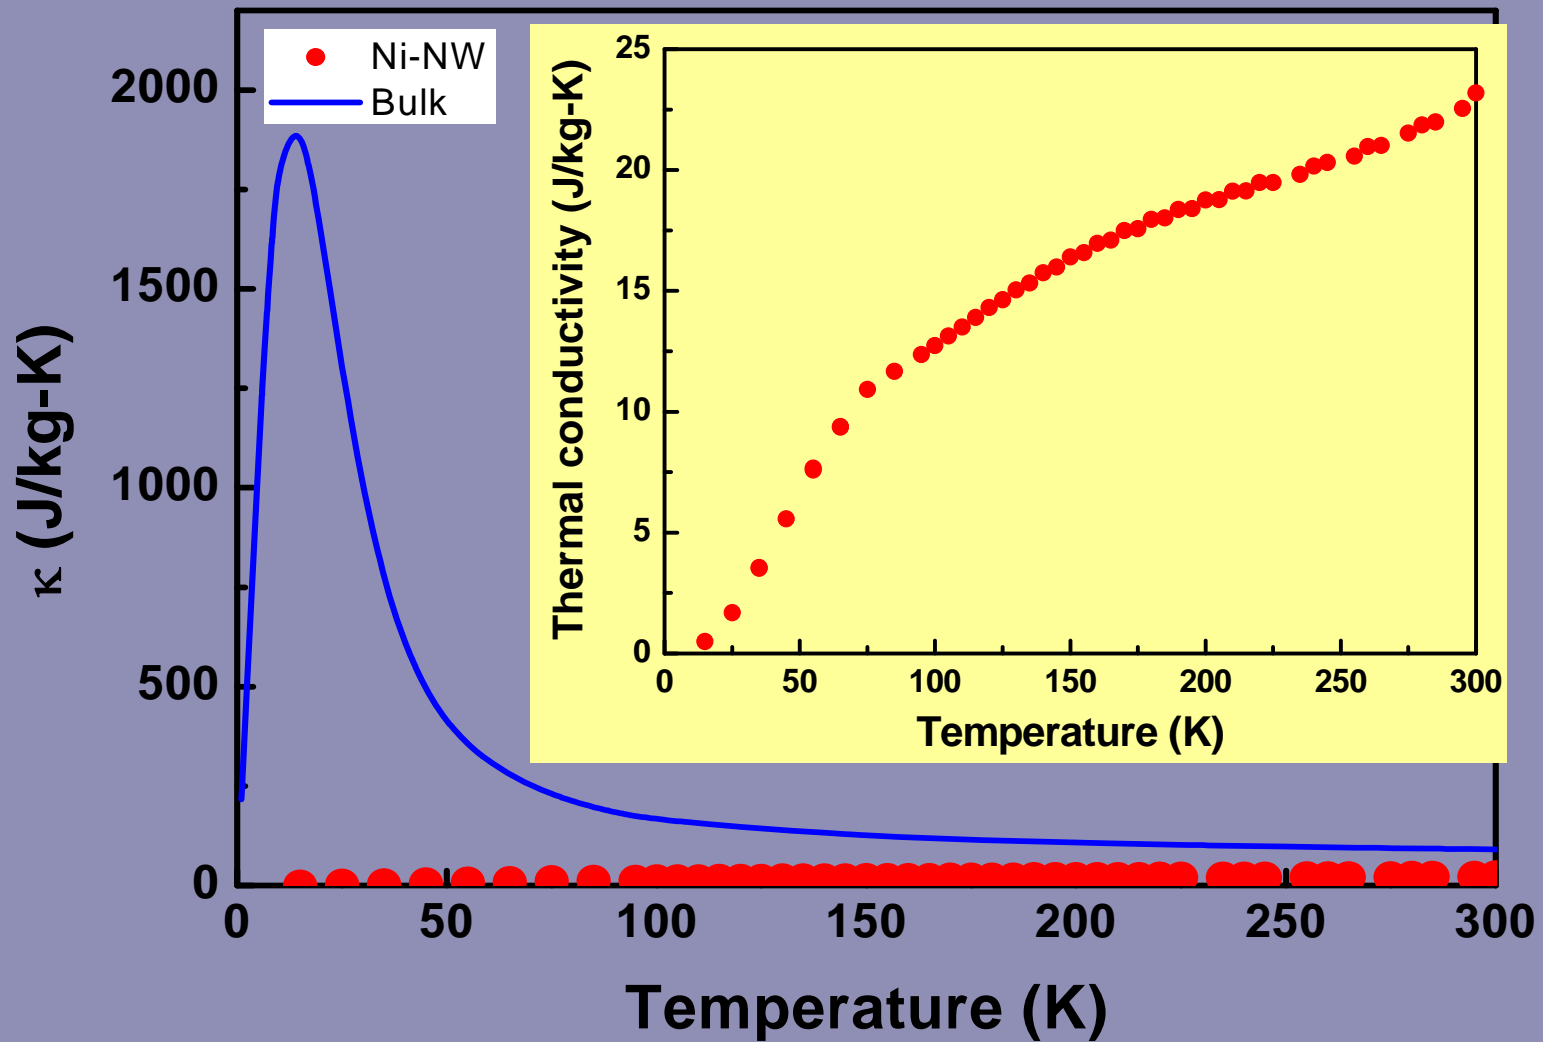

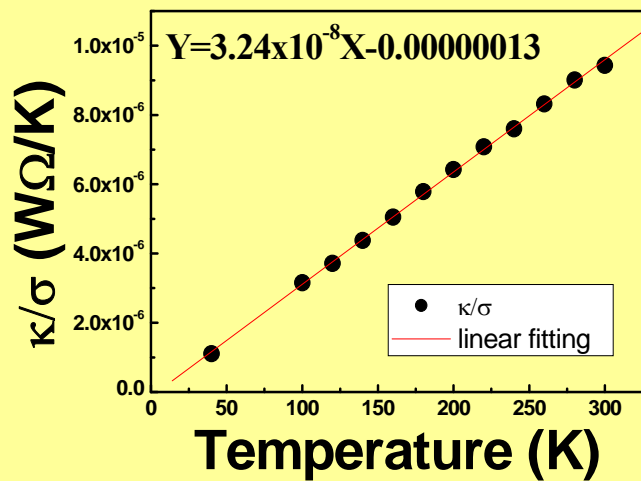


$$V_{3\omega} \approx \frac{4I^3 L R R'}{\pi^4 \kappa S \sqrt{1 + (2\omega\gamma)^2}}$$

Lorenz number  $L_0$


$$L_0 = \frac{\kappa}{\sigma T} = \frac{1}{3} \left( \frac{\pi k_B}{e} \right)^2$$

$$= 2.45 \times 10^{-8} \text{ W}\cdot\Omega/\text{K}^2$$

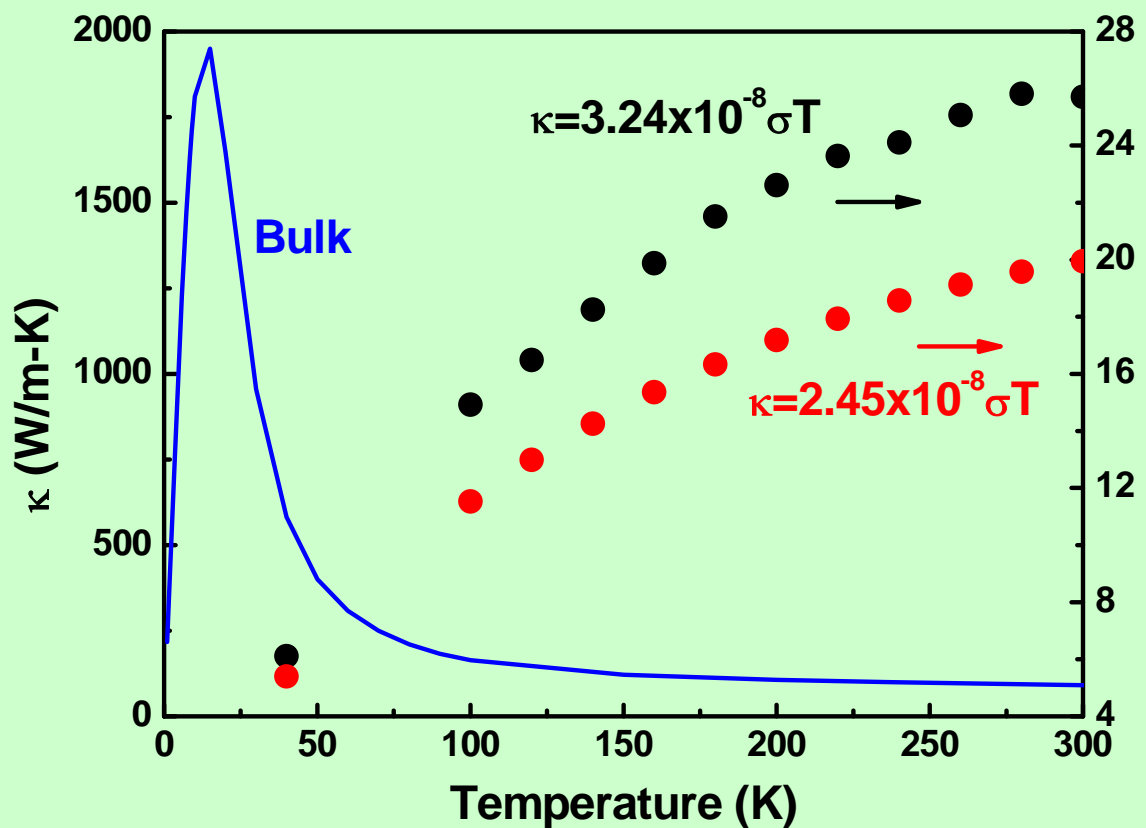


Wiedemann-Franz law  $\kappa_e = \sigma L_0 T$


## ZT ( $\propto \sigma/\kappa$ ) of Ni-nanowire vs. Bulk

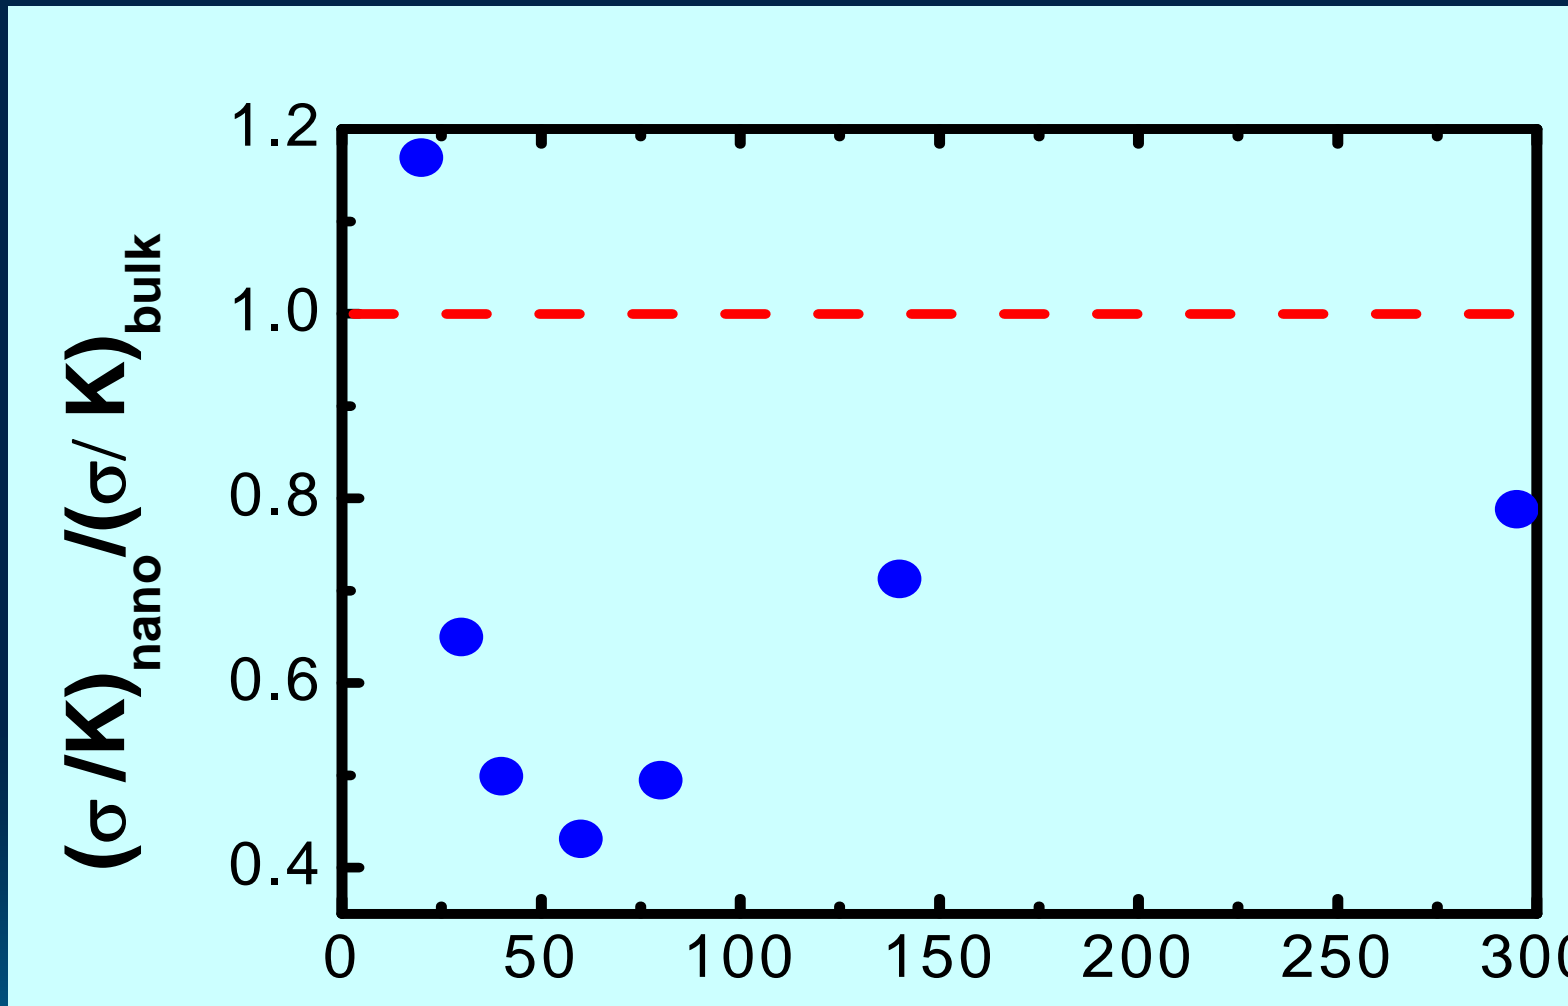

Is the diameter in the quantum size regime? Need to make a smaller diameter wire  $\sim 10$  nm?

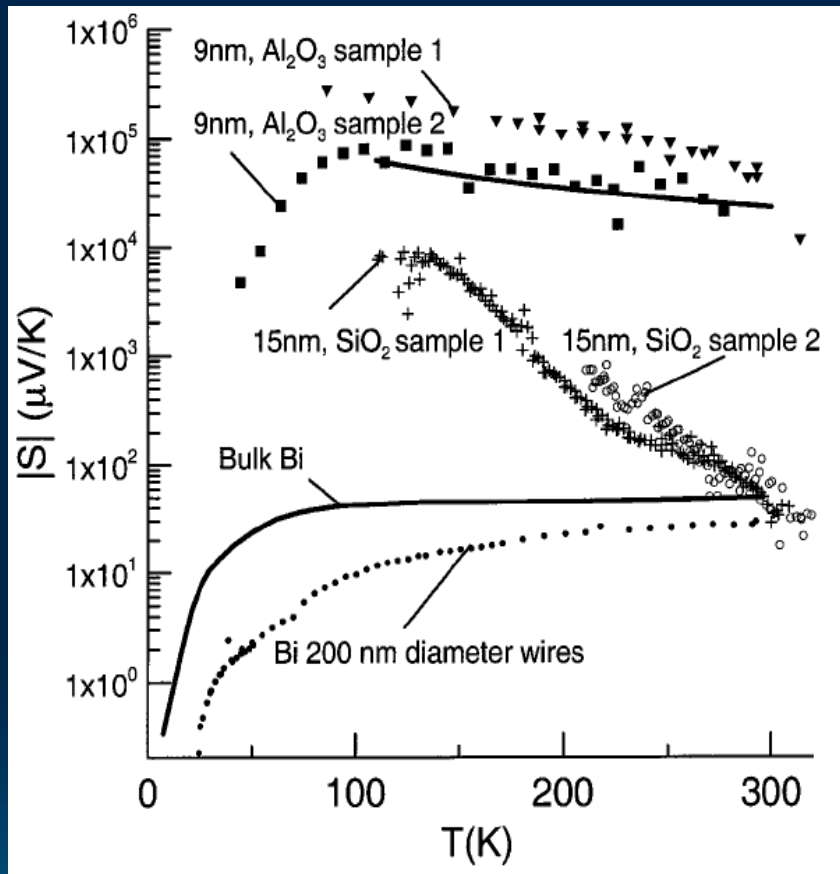


J.P. Heremans, et al., PRL **88**, 216801-1 (2002)

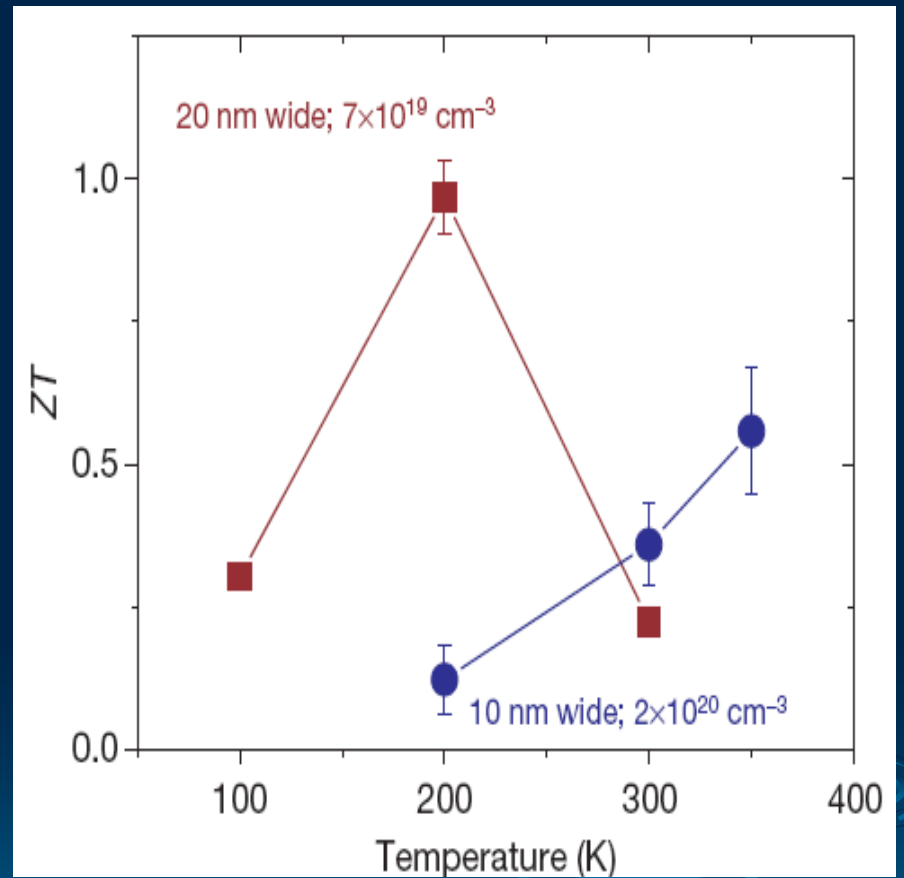


A.I. Boukai, et al., Nature **451**, 168 (2008)



# Nanostructures

- Transport properties-phonon, electron,...
- Lattice structure □ disorder
- Dimension □ Size effect
- Spin dependence
- **Shape**

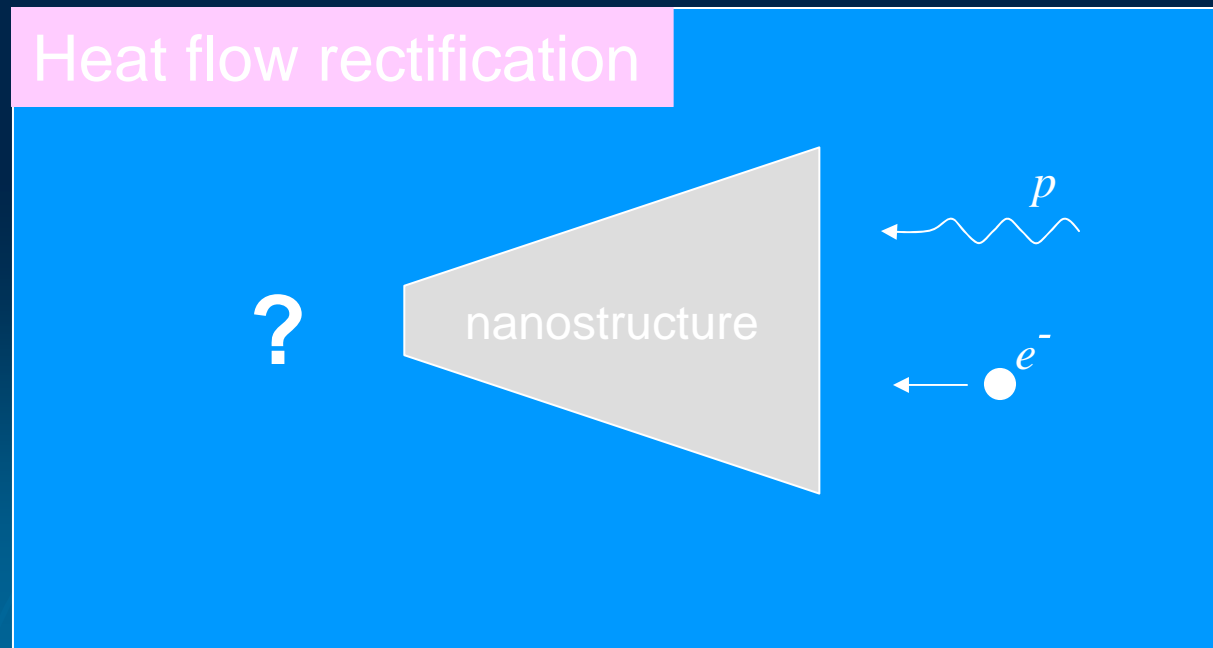

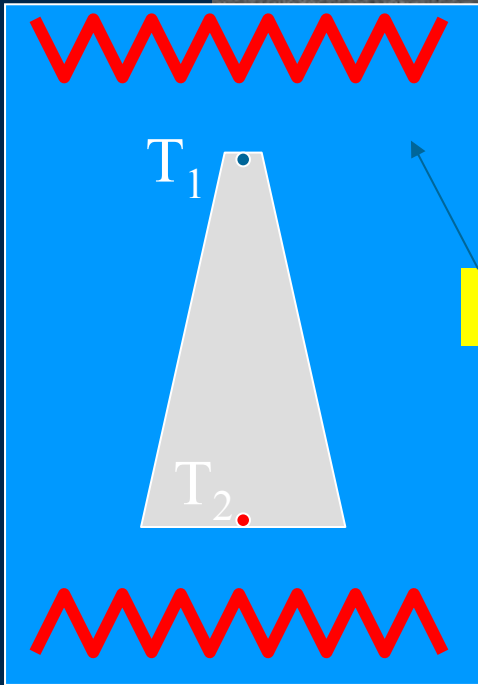


Heater

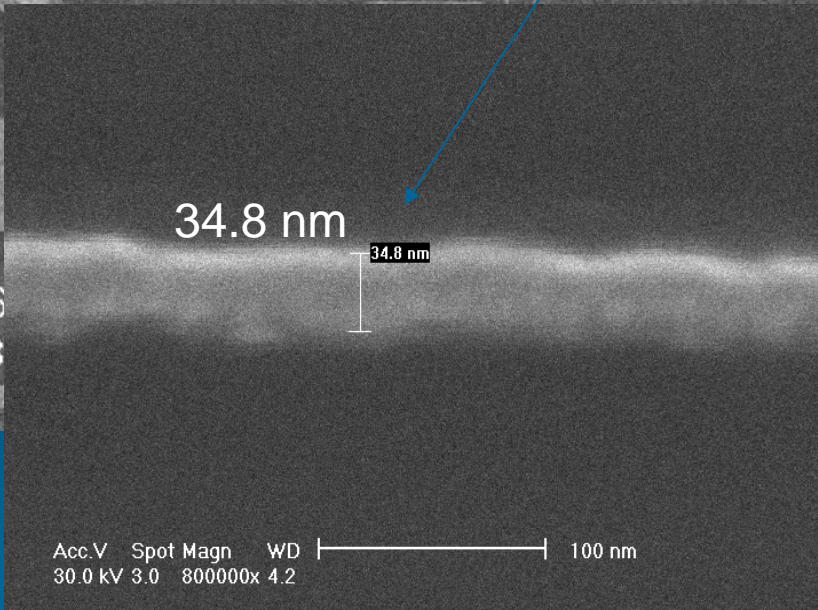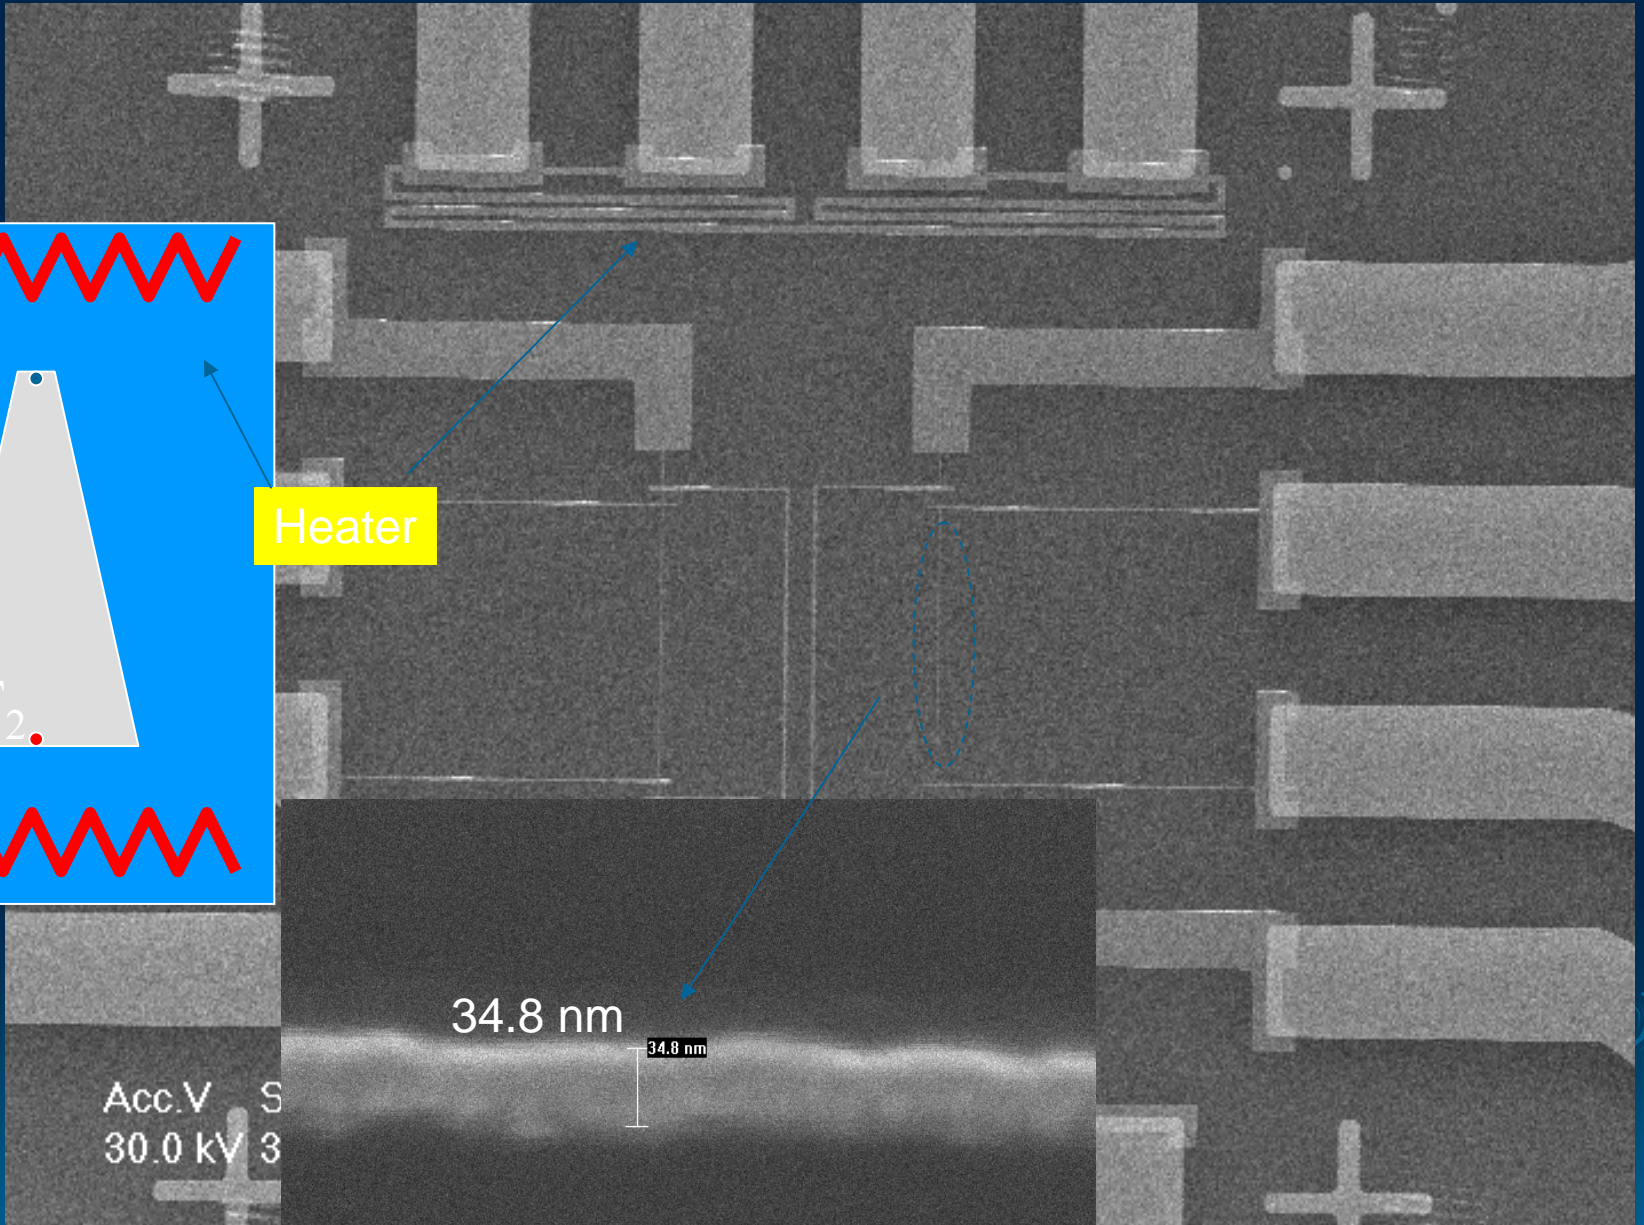

Acc.V 30.0 kV  
Spot 3.0

Acc.V 30.0 kV Spot 3.0 Magn 800000x WD 4.2 |-----| 100 nm

**Thermo-power measurement on a suspended single  
Ni-nanowire ( $\Phi=200$  nm  $L=10$   $\mu\text{m}$  )  
Results to appear in APL 2008 Febuary issue**

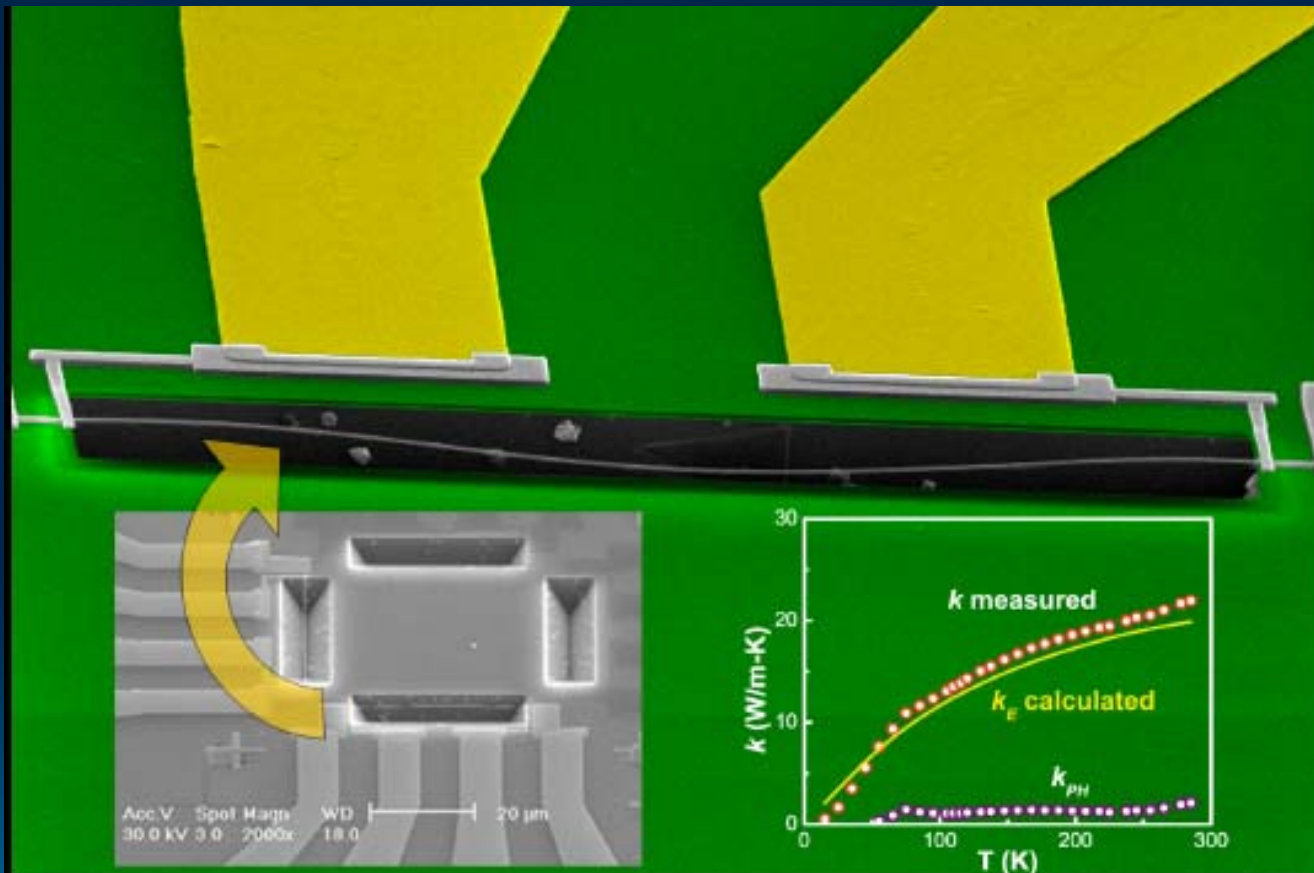

**The graph was used on the Cover of APL 11 Feb issue**

# Summary

- ④ A lithographic process has been developed to construct the suspended structure.
- ④ The self-heating  $3\omega$  method and measurement system for nanoscale materials has been constructed.
- ④ The thermal conductivity and specific heat of diameter  $\sim 180$  nm nickel wire are 23 W/m-K and 64.6 J/mol-K (at 25 $\square$ ), respectively.
- ④ A 30 nm nano-wire has been fabricated to demonstrate our capability