

REPORT DOCUMENTATION PAGE			Form Approved OMB NO. 0704-0188		
The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA, 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE (DD-MM-YYYY) 25-10-2007		2. REPORT TYPE Final Report		3. DATES COVERED (From - To) 1-Jul-2006 - 30-Jun-2007	
4. TITLE AND SUBTITLE Synthesis of Nanostructured LaB6 Powders			5a. CONTRACT NUMBER W911NF-06-1-0226		
			5b. GRANT NUMBER		
			5c. PROGRAM ELEMENT NUMBER 6620AC		
6. AUTHORS Olivia A. Graeve			5d. PROJECT NUMBER		
			5e. TASK NUMBER		
			5f. WORK UNIT NUMBER		
7. PERFORMING ORGANIZATION NAMES AND ADDRESSES University of Nevada - Reno Office of Sponsored Projects Administration/325 2215 Raggio Parkway Reno, NV 89512 -			8. PERFORMING ORGANIZATION REPORT NUMBER		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army Research Office P.O. Box 12211 Research Triangle Park, NC 27709-2211			10. SPONSOR/MONITOR'S ACRONYM(S) ARO		
			11. SPONSOR/MONITOR'S REPORT NUMBER(S) 50998-MS.1		
12. DISTRIBUTION AVAILABILITY STATEMENT Approved for public release; Federal purpose rights					
13. SUPPLEMENTARY NOTES The views, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy or decision, unless so designated by other documentation.					
14. ABSTRACT Nanocrystalline powders of LaB6 with an average crystallite size of 20 nm, as determined from x-ray diffraction analysis, have been obtained using a combustion synthesis technique that makes use of lanthanum nitrate, boron, and carbonylhydrazide as precursors. The optimum fuel-to-oxidizer ratio was found to be 0.25, which is quite low compared to typical combustion synthesis experiments. The powders are phase-pure except for about a 3 mol% contamination of LaBO3.					
15. SUBJECT TERMS lanthanum hexaboride, combustion synthesis, carbonylhydrazide, nanopowders					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT SAR	15. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON Olivia Graeve
a. REPORT U	b. ABSTRACT U	c. THIS PAGE U			19b. TELEPHONE NUMBER 775-784-7098

Report Title

Synthesis of Nanostructured LaB6 Powders

ABSTRACT

Nanocrystalline powders of LaB6 with an average crystallite size of 20 nm, as determined from x-ray diffraction analysis, have been obtained using a combustion synthesis technique that makes use of lanthanum nitrate, boron, and carbonylhydrazide as precursors. The optimum fuel-to-oxidizer ratio was found to be 0.25, which is quite low compared to typical combustion synthesis experiments. The powders are phase-pure except for about a 3 mol% contamination of LaBO3.

List of papers submitted or published that acknowledge ARO support during this reporting period. List the papers, including journal references, in the following categories:

(a) Papers published in peer-reviewed journals (N/A for none)

Number of Papers published in peer-reviewed journals: 0.00

(b) Papers published in non-peer-reviewed journals or in conference proceedings (N/A for none)

Number of Papers published in non peer-reviewed journals: 0.00

(c) Presentations

Number of Presentations: 0.00

Non Peer-Reviewed Conference Proceeding publications (other than abstracts):

Number of Non Peer-Reviewed Conference Proceeding publications (other than abstracts): 0

Peer-Reviewed Conference Proceeding publications (other than abstracts):

Number of Peer-Reviewed Conference Proceeding publications (other than abstracts): 0

(d) Manuscripts

Number of Manuscripts: 0.00

Number of Inventions:

Graduate Students

<u>NAME</u>	<u>PERCENT SUPPORTED</u>
Amrita Mishra	0.61
Raghunath Kanakala	0.16
Abhiram Madadi	0.11
Kaustav Sinha	0.11
FTE Equivalent:	0.99
Total Number:	4

Names of Post Doctorates

<u>NAME</u>	<u>PERCENT SUPPORTED</u>
FTE Equivalent:	
Total Number:	

Names of Faculty Supported

<u>NAME</u>	<u>PERCENT SUPPORTED</u>	National Academy Member
Olivia A. Graeve	1.00	No
FTE Equivalent:	1.00	
Total Number:	1	

Names of Under Graduate students supported

<u>NAME</u>	<u>PERCENT SUPPORTED</u>
Karla Hernandez	0.64
Brandon Williams	0.34
Adriana Velasquez	0.02
FTE Equivalent:	1.00
Total Number:	3

Student Metrics

This section only applies to graduating undergraduates supported by this agreement in this reporting period

The number of undergraduates funded by this agreement who graduated during this period: 0.00

The number of undergraduates funded by this agreement who graduated during this period with a degree in science, mathematics, engineering, or technology fields:..... 0.00

The number of undergraduates funded by your agreement who graduated during this period and will continue to pursue a graduate or Ph.D. degree in science, mathematics, engineering, or technology fields:..... 0.00

Number of graduating undergraduates who achieved a 3.5 GPA to 4.0 (4.0 max scale):..... 0.00

Number of graduating undergraduates funded by a DoD funded Center of Excellence grant for Education, Research and Engineering:..... 0.00

The number of undergraduates funded by your agreement who graduated during this period and intend to work for the Department of Defense 0.00

The number of undergraduates funded by your agreement who graduated during this period and will receive scholarships or fellowships for further studies in science, mathematics, engineering or technology fields: 0.00

Names of Personnel receiving masters degrees

<u>NAME</u>

Total Number:

Names of personnel receiving PhDs

<u>NAME</u>

Total Number:

Names of other research staff

<u>NAME</u>

<u>PERCENT SUPPORTED</u>

FTE Equivalent:

Total Number:


Sub Contractors (DD882)

Inventions (DD882)

Synthesis of Nanostructured LaB₆ Powders

Olivia A. Graeve
Assistant Professor
Chemical and Metallurgical Engineering
University of Nevada, Reno
1664 N. Virginia Street – Mail Stop 388
Reno, NV 89557
Tel: (775) 784-7098
Fax: (775) 327-5059
Email: oagraeve@unr.edu


FINAL REPORT

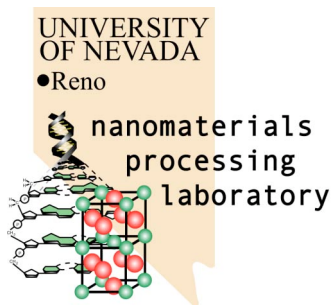

1. INTRODUCTION

The goal of this project was to demonstrate the feasibility of preparing LaB₆ powders with an average particle size of around 50 nm via a combustion process.

Combustion synthesis [1, 2, 3, 4] has been under development in the last twenty years, and offers many advantages for the formation of ultra-fine powders. It is a wet chemical precipitation process in which an exothermic reaction between precursor components is utilized. The exothermic reaction occurs between metal nitrates and a carbonaceous fuel in a rapid and self-sustaining manner. The type of fuel and the fuel-to-nitrate ratio are the most important controlling parameters for determining the reaction temperature reached during combustion [5, 6]. In a typical combustion reaction, the precursor mixture, which is diluted in a small amount of solvent and placed in a low-temperature muffle furnace, dehydrates and ruptures into a flame in less than five minutes. As an example, the reaction shown below for Y₂O₃



is such that the products contain the desired voluminous, foamy material and gases that escape during the reaction. The gaseous products carry heat away from the system, hindering particle growth, and allowing the synthesis of powders with crystallites of nanometer dimensions, as has been shown in our recent publication [7]. The gases increase the surface area of the powders by creating micro- and nano-porous regions within the reaction zone. Computer modeling studies have shown that there are over one hundred possible product species that can be formed during the reaction [8]. However, most of the products exist in such small amounts that they can be ignored. The material in this study was synthesized using carbohydrazide (CH₆N₄O) as a fuel, since it has two desirable features: (1) it produces a very high reaction temperature, and (2) it complexes with the metal cations thereby increasing their solubility and preventing selective precipitation from occurring as the water is evaporated during the reaction. The carbohydrazide molecule has two amine groups, both of which are available to participate in the complexation of metal ions [9].

2. TECHNICAL OBJECTIVES

The specific objectives of this project were:

- (1) To synthesize nanostructured powders of lanthanum hexaboride using a combustion synthesis process, and
- (2) to characterize the process of synthesis over a range of experimental conditions in order to optimize the process.

3. EXPERIMENTAL RESULTS

Figure 1 illustrates the steps that were followed for the synthesis of the powders. The precursor materials, listed in **Table 1**, were mixed according to the following equation:

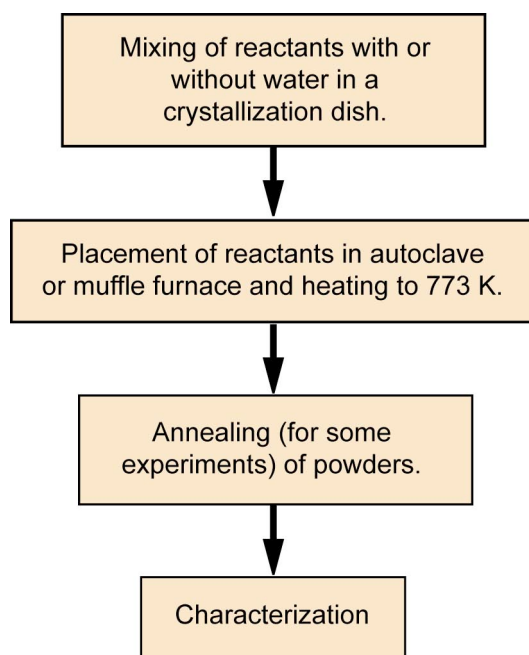



Figure 1. Process flow chart for the synthesis and characterization of the LaB₆ powders.

In regards to the viability of the process during synthesis, we have determined the optimum processing conditions for obtaining the desired powders. The parameters that were studied include:

The fuel-to-nitrate ratio is the most important parameter for the determination of the particle size and purity of the final powders, since the amount of fuel in the system determines the temperature of combustion. The mixtures that were attempted are listed in **Table 2**.

Table 1. Precursors for the synthesis of LaB₆ powders.

Precursor	Properties
$\text{La}(\text{NO}_3)_3$ Lanthanum (III) nitrate hydrate Supplier: Sigma Aldrich Catalog No: 238554	Purity: 99.9% Physical State at Room Temperature: Crystalline.
B Boron Supplier: Sigma Aldrich Catalog No: 2311512	Physical State at Room Temperature: Amorphous powder.
$(\text{H}_2\text{NNH})_2\text{C}=\text{O}$ Carbohydrazide Supplier: Sigma Aldrich Catalog No: C11006	Purity: 98% Physical State at Room Temperature: Solid.

Table 2. Listing of all combustion experiments attempted for the project.

Fuel-to-oxidizer ratio, ϕ	Reactant amounts	Experimental conditions	Results
Experiment 1: $\phi = 4$	$m_{\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}} = 10.6249 \text{ g}$ $m_{\text{B}} = 1.5916 \text{ g}$ $m_{\text{carbohydrazide}} = 8.8418 \text{ g}$	Experiment in muffle furnace at 500°C using water as a solvent.	The combustion experiment resulted in a mixture of La ₂ O ₃ and LaBO ₃ . Clearly the fuel-to-oxidizer ratio is too high and results in full oxidation of the reactants.
Experiment 2: $\phi = 0.75$	$m_{\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}} = 10.6249 \text{ g}$ $m_{\text{B}} = 1.5916 \text{ g}$ $m_{\text{carbohydrazide}} = 1.6578 \text{ g}$	Experiment in muffle furnace at 500°C using water as a solvent.	The x-ray diffraction analysis shows the formation of the LaB ₆ phase. However, there are significant amounts of LaBO ₃ phase. The color of the powder is brownish/purple, a sure sign for the presence of LaB ₆ , which is purple, and LaBO ₃ , which is brown.
Experiment 3: $\phi = 0.5$	$m_{\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}} = 10.6249 \text{ g}$ $m_{\text{B}} = 1.5916 \text{ g}$ $m_{\text{carbohydrazide}} = 1.1052 \text{ g}$	Experiment in muffle furnace at 500°C using water as a solvent.	The x-ray diffraction analysis shows the formation of the LaB ₆ phase, with smaller amounts of the LaBO ₃ phase.

Experiment 4: $\phi = 0.25$	$m_{\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}} = 10.6249 \text{ g}$ $m_{\text{B}} = 1.5916 \text{ g}$ $m_{\text{carbohydrazide}} = 0.5526 \text{ g}$	Experiment in muffle furnace at 500°C using water as a solvent.	The x-ray diffraction analysis shows the formation of the LaB_6 phase, with even smaller amounts of the LaBO_3 phase compared to the experiment at the $\phi = 0.5$.
Experiment 5: $\phi = 0.75$	$m_{\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}} = 10.6249 \text{ g}$ $m_{\text{B}} = 1.5916 \text{ g}$ $m_{\text{carbohydrazide}} = 1.6578 \text{ g}$	Experiment in muffle furnace starting at room temperature and heating to the combustion temperature of 320°C without any water. Elimination of water was attempted with the intent of reducing sources of oxygen further.	Same as experiment 2, but with smaller amounts of LaBO_3 .
Experiment 6: $\phi = 0.5$	$m_{\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}} = 10.6249 \text{ g}$ $m_{\text{B}} = 1.5916 \text{ g}$ $m_{\text{carbohydrazide}} = 1.1052 \text{ g}$	Experiment in muffle furnace starting at room temperature and heating to the combustion temperature of 320°C without any water.	Same as experiment 3, but with minimal amounts of LaBO_3 (about 3 mol%).
Experiment 7: $\phi = 0.25$	$m_{\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}} = 10.6249 \text{ g}$ $m_{\text{B}} = 1.5916 \text{ g}$ $m_{\text{carbohydrazide}} = 0.5526 \text{ g}$	Experiment in muffle furnace starting at room temperature and heating to the combustion temperature of 320°C without any water.	Same as experiment 3, but with minimal amounts of LaBO_3 (about 3 mol%).
Experiment 8: $\phi = 0.25$	$m_{\text{La}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}} = 10.6249 \text{ g}$ $m_{\text{B}} = 1.5916 \text{ g}$ $m_{\text{carbohydrazide}} = 0.5526 \text{ g}$	Experiment in the protected argon atmosphere of an autoclave starting at room temperature and heating to the combustion temperature of 360°C without any water.	The x-ray diffraction analysis shows the formation of the LaBO_3 phase, with minimal amounts of LaB_6 . We have concluded that there are still significant amounts of oxygen present during this reaction and that the LaBO_3 stable phase forms due to the extended higher temperatures the sample experiences during the cooling of the autoclave. The oxygen is a result of the combustion of the carbohydrazide.

As described for experiments 6 and 7, the exact phase of LaB_6 is achieved, but the LaBO_3 phase persists in amounts of 3 mol%. The best experiments were done in a muffle furnace with only small amount of fuel, which is unusual for combustion synthesis reactions that normally require larger amounts of fuel. The formation of the LaB_6 phase requires careful control of the temperature of reaction and immediate quenching so as not to promote the formation of the more stable LaBO_3 phase. The extended cooling times in the autoclave does not allow quenching of the experiment. Hence, the powders obtained for this case are mostly LaBO_3 . The source of oxygen is the carbohydrazide. Elimination of the residual LaBO_3 might be possible by switching to a fuel that does not contain oxygen, such as hydrazine.

The powders from experiments 6 and 7 are the best results we have obtained. **Figure 2** shows the XRD results for these experiments.

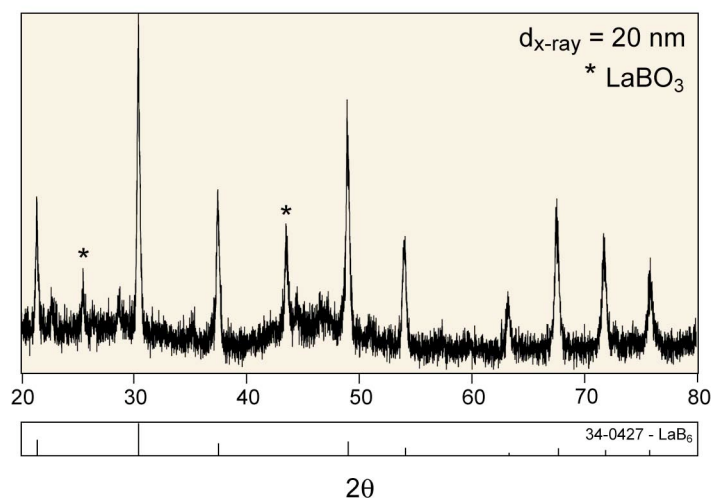


Figure 2. X-ray diffraction analysis of powders obtained using a fuel-to-oxidizer ratio of 0.25 in a muffle furnace without any solvent use for the reactants.

We have attempted to characterize the powders using scanning and transmission electron microscopy, but the powders are such strong electron emitters that it has proved impossible to focus the electron beam from the microscope column. The electrons from the sample act as strong scatterers for the electron beam, which results in images that are completely out of focus.

4. CONCLUSIONS

Nanocrystalline powders of LaB_6 with an average crystallite size of 20 nm, as determined from x-ray diffraction analysis, have been obtained using a combustion synthesis technique that makes use of lanthanum nitrate, boron, and carbohydrazide as precursors. The optimum fuel-to-oxidizer ratio was found to be 0.25, which is quite low compared to typical combustion synthesis experiments. The powders are phase-pure except for about a 3 mol% contamination of LaBO_3 .

5. PROPOSED FUTURE WORK

1. Synthesis of the powders using hydrazine as a fuel. This fuel does not contain oxygen in its chemical formula.
2. Synthesis of the powders in a muffle furnace that allows rapid quenching of the experiment, but in an argon atmosphere. Currently our muffle furnace does not have that capability. The use of an autoclave is not advisable due to the long cooling times required for the experiment, which results in conversion of the LaB_6 into LaBO_3 and grain growth.
3. Development of an appropriate technique to image the powders using electron microscopy.

6. REFERENCES

-
- [1]. G. Tessari, M. Bettinelli, A. Speghini, D. Ajò, G. Pozza, L.E. Depero, B. Allieri, and L. Sangaletti, "Synthesis and optical properties of nanosized powders: lanthanide-doped Y_2O_3 ," *Appl. Surf. Sci.*, **144-145**, 686-689 (1999).
 - [2]. J.A. Copabianco, F. Vetrone, T. D'Alesio, G. Tessari, A. Speghini, and M. Bettinelli, "Optical spectroscopy of nanocrystalline $\text{Y}_2\text{O}_3:\text{Er}^{3+}$ obtained by combustion synthesis," *Phys. Chem. Chem. Phys.*, **2** [14] 3203-3207 (2000).
 - [3]. E. Zych, "On the reasons for low luminescence efficiency in combustion-made $\text{Lu}_2\text{O}_3:\text{Tb}$," *Opt. Mater.*, **16** [4] 445-452 (2001).
 - [4]. J. McKittrick, L.E. Shea, C.F. Bacalski, E.J. Bosze, "The influence of processing parameters on luminescent oxides produced by combustion synthesis," *Displays*, **19** [4] 169-172 (1999).
 - [5]. L.E. Shea, J. McKittrick, O.A. Lopez, and E. Sluzky, "Effect of processing parameters on luminescence of combustion-synthesized, rare earth-activated $\text{Y}_3\text{Al}_5\text{O}_{12}$ phosphors," *Ceram. Trans.*, **67**, 105-108 (1996).
 - [6]. L.E. Shea, J. McKittrick, O.A. Lopez, E. Sluzky, and M.L.F. Phillips, "Advantages of self-propagating combustion reactions for synthesis of oxide phosphors," *J. Soc. Inf. Disp.*, **5** [2] 117-125 (1997).
 - [7]. O.A. Graeve, S. Varma, G. Rojas-George, D. Brown, and E.A. Lopez, "Synthesis and Characterization of Luminescent Yttrium Oxide Doped with Tm and Yb," *Journal of the American Ceramic Society*, **89** [3] 926-931 (2006).
 - [8]. J. McKittrick, E.J. Bosze, C.F. Bacalski, and L.E. Shea, "Physical properties of combustion synthesized oxide powders"; pp. 139-157 in Miner. Metals & Mater. Society Symposium Proceedings, *Powder Materials: Current Research and Industrial Practices*. Edited by E.D.S. Marquis. Miner. Metals & Mater. Society, Warrendale, PA, 1999.
 - [9]. O.A. Lopez, J. McKittrick, and L.E. Shea, "Fluorescence properties of polycrystalline Tm^{3+} -activated $\text{Y}_3\text{Al}_5\text{O}_{12}$ and $\text{Tm}^{3+}\text{-Li}^+$ co-activated $\text{Y}_3\text{Al}_5\text{O}_{12}$ in the visible and near IR ranges," *J. Lum.*, **71** [1] 1-11 (1997).