

Formation of An Oxygen-Deficient Y_2O_3 Phase Under High Pressure



**Center for Nanomaterials Research
Rutgers University**

Contact:

Jafar F. Al-Sharab
jafarhan@rci.rutgers.edu

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE JUN 2010		2. REPORT TYPE N/A		3. DATES COVERED -	
4. TITLE AND SUBTITLE Formation of An Oxygen-Deficient Y2O3Phase Under High Pressure				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Rutgers University				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release, distribution unlimited					
13. SUPPLEMENTARY NOTES See also ADM002307. ECI International Conference on Sub-Micron and Nanostructured Ceramics Held in Colorado Springs, Colorado on 7-12 June 2009, The original document contains color images.					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UU	18. NUMBER OF PAGES 19	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

Formation of An Oxygen-Deficient Y_2O_3 Phase Under High Pressure

Polycrystalline Y_2O_3 is the material of choice for IR applications since it has excellent optical properties in the visible, and near infra-red band.


Current processing methods yield polycrystalline Y_2O_3 with large grain size ($> 100 \mu m$), which limits the hardness and erosion resistance attainable.

One way to improve strength is to develop an ultra-fine grained material with acceptable optical transmission properties.

It has been found recently that reversible transformation in consolidated Y_2O_3 under high pressure and temperature materials led to an extraordinary reduction in grain size .

Holding consolidated Y_2O_3 material under high pressure and temperature also yielded a novel surface structural modification


Phase Transformation under High pressure of consolidated Y_2O_3 samples

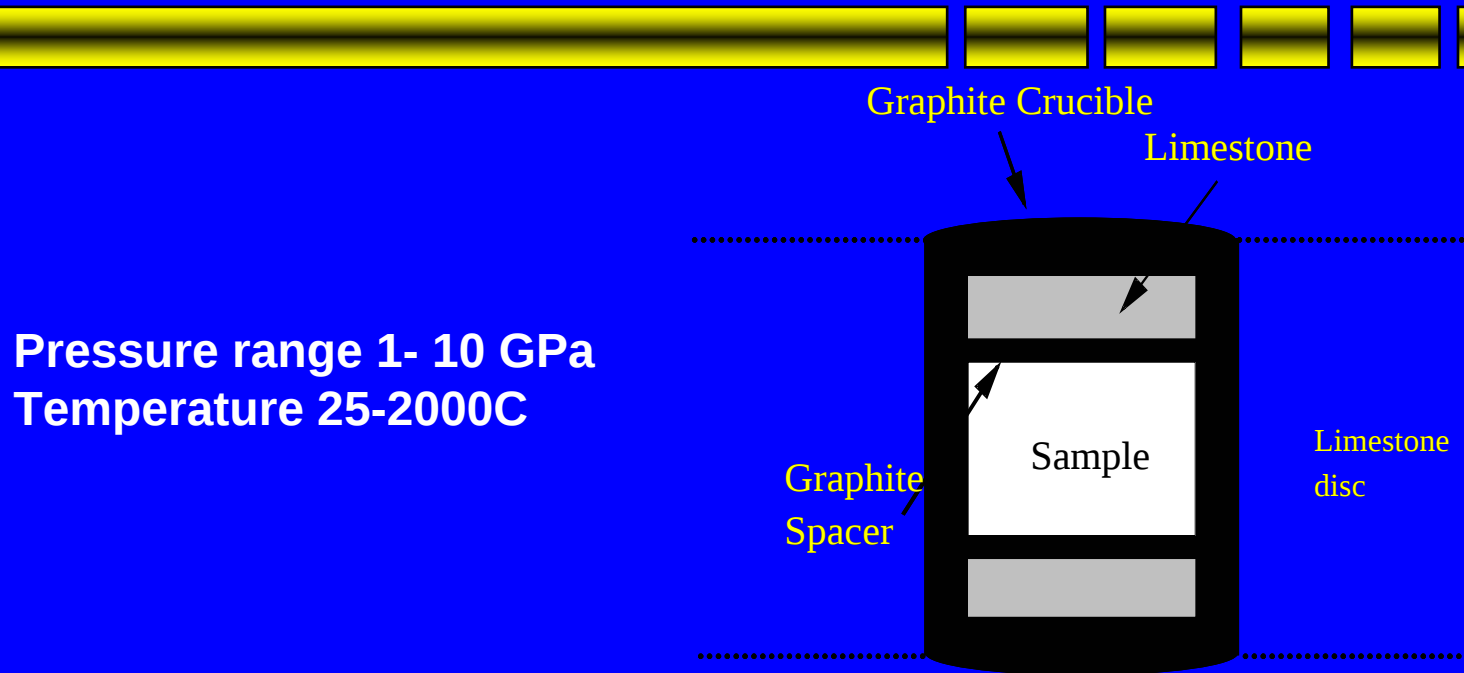

Resistive heating of graphite crucible enables rapid heating up to operating temperature

- High pressure (8GPa/1000C/1-15min) has been utilized for grain size refinement (300 μm $\rightarrow$ $\sim$ 100 nm) via reversible transformation (cubic $\rightarrow$ monoclinic $\rightarrow$ cubic)

Surface columnar grains and grains size refinement in Y_2O_3 after hot pressing at 8 GPa/1000°C


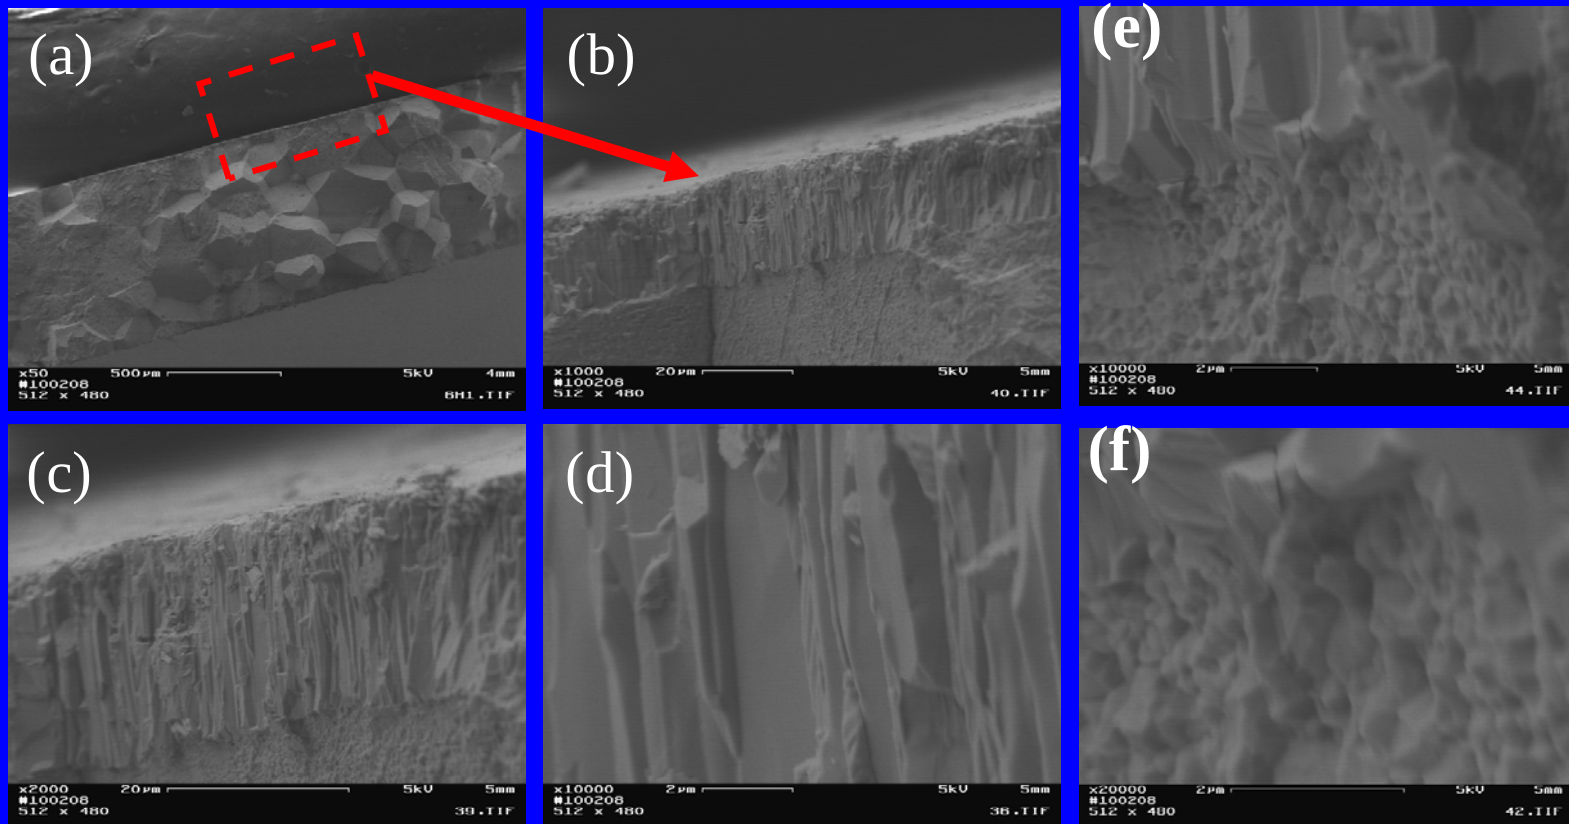


Sample was processed at 8 GPa/1000°C for 6 hours

Predominantly intergranular fracture, apparently along grain boundaries of the *original* coarse-grained ($\sim 300\ \mu\text{m}$) cubic- Y_2O_3 has been observed






Sample's surface exhibit columnar grains while sample's interior was transformed under pressure into nano-grained ($\sim 100\ \text{nm}$) monoclinic- Y_2O_3

Hardness measurements using nano indentation

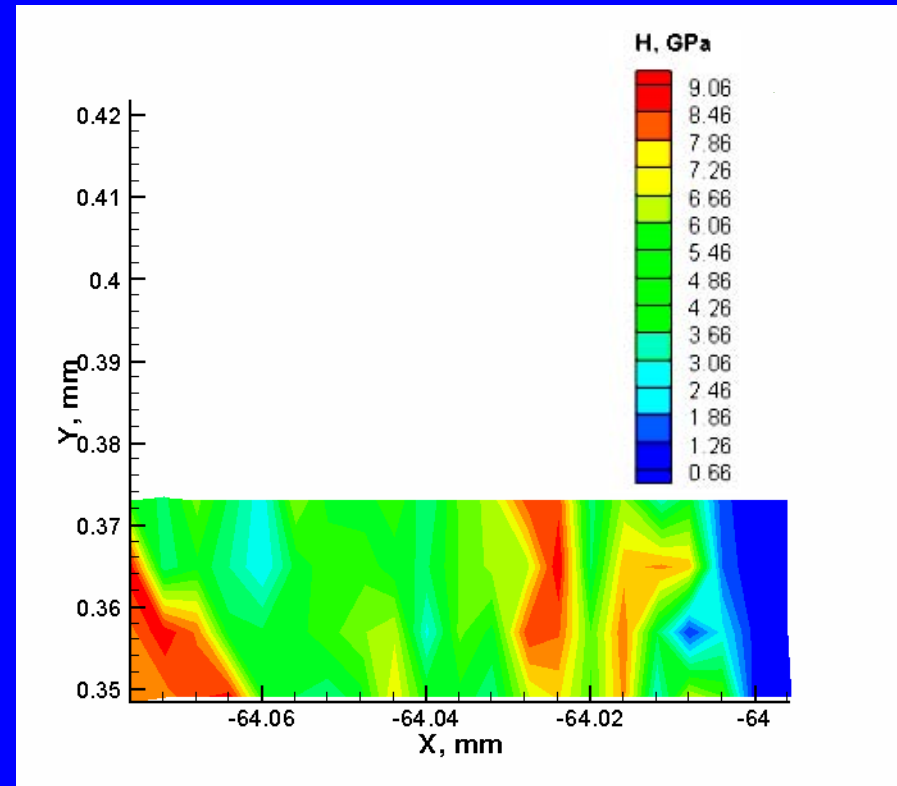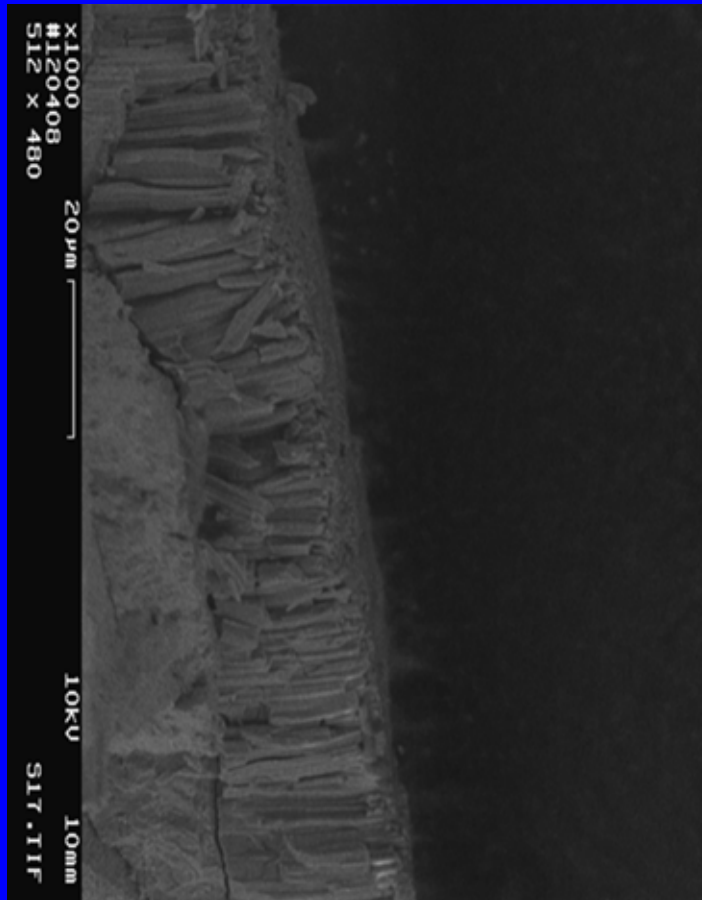

- Columnar grains showed ~ an order of magnitude lower hardness than the sample interior
- This difference in hardness must be due to chemical and structural differences

EDS analysis of fractured surface

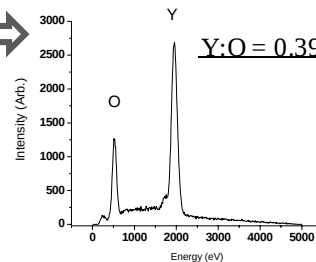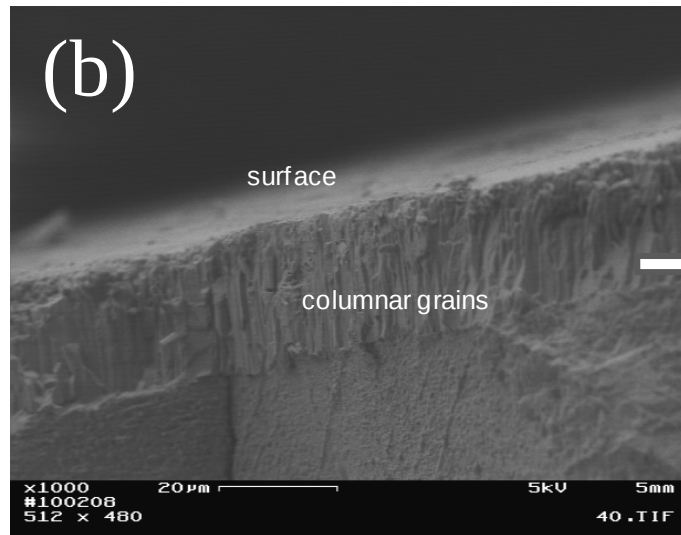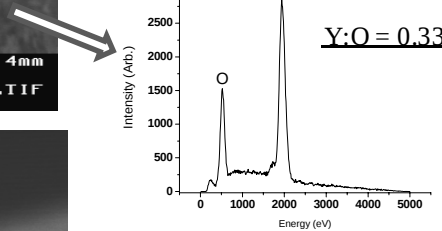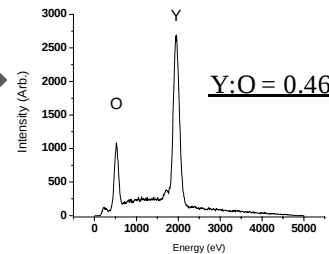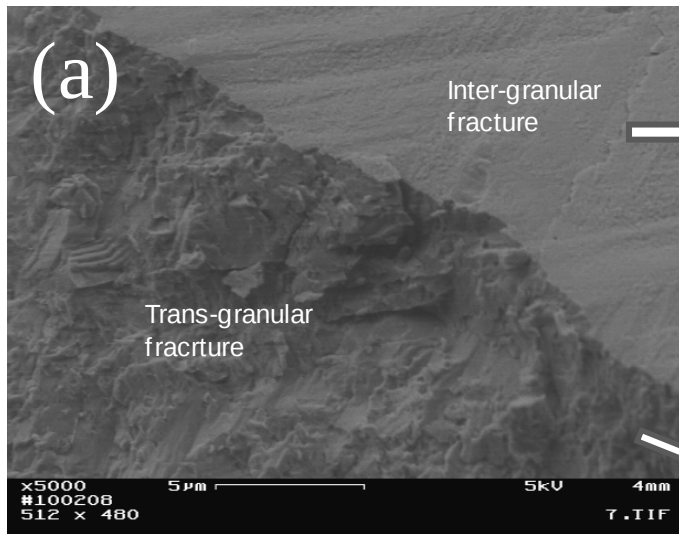



EDS analysis of a fractured sample, comparing the Y/O ratios for the smooth intergranular fracture, rough transgranular fracture, and faceted columnar-grained structure

Y_2O_3 is reported to lose oxygen at high temperatures and a formation of $Y_2O_{2.88}$ is possible¹

Y_2O_3 is reported to lose oxygen on heating at high temperatures; a stoichiometry of $Y_2O_{2.88}$ at 1800°C is reported.¹

¹. R. J. Ackermann, E. G. Rauh, and R. R. Walters, *J. Chem. Thermodyn.*, 2 [1] 139-149 (1970).



TEM Analysis

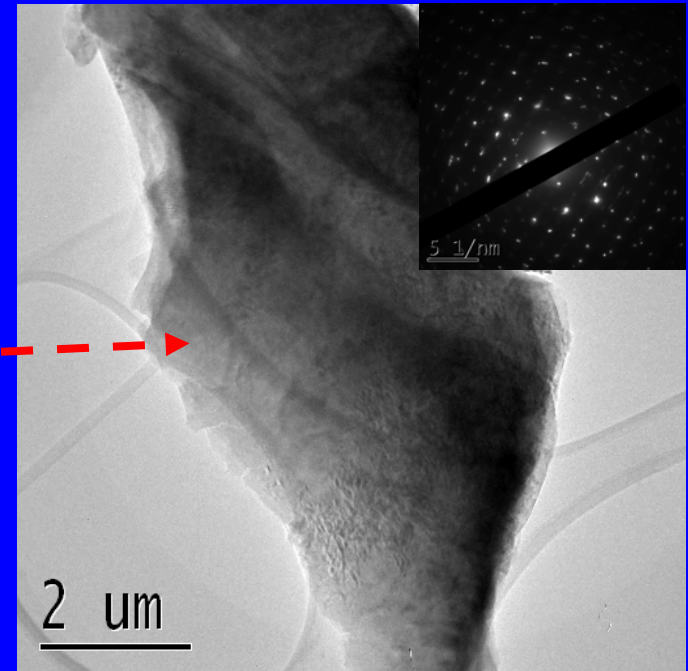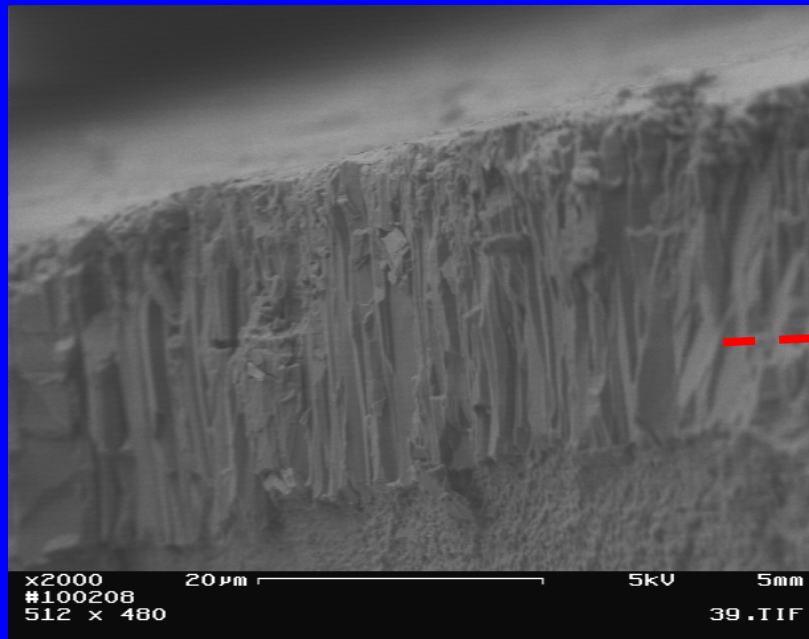

- TEM sample has been prepared by scraping the surface onto copper grid
- Electron-transparent columnar grains with same dimensions and aspect ratio from SEM were observed





Measured d-spacings (nm)	(hkl) Cubic, Ia-3
0.443	(211)
0.353	(220)
0.297	(222)
0.258	(400)
0.189	(440)

HRTEM imaging and FFT analysis

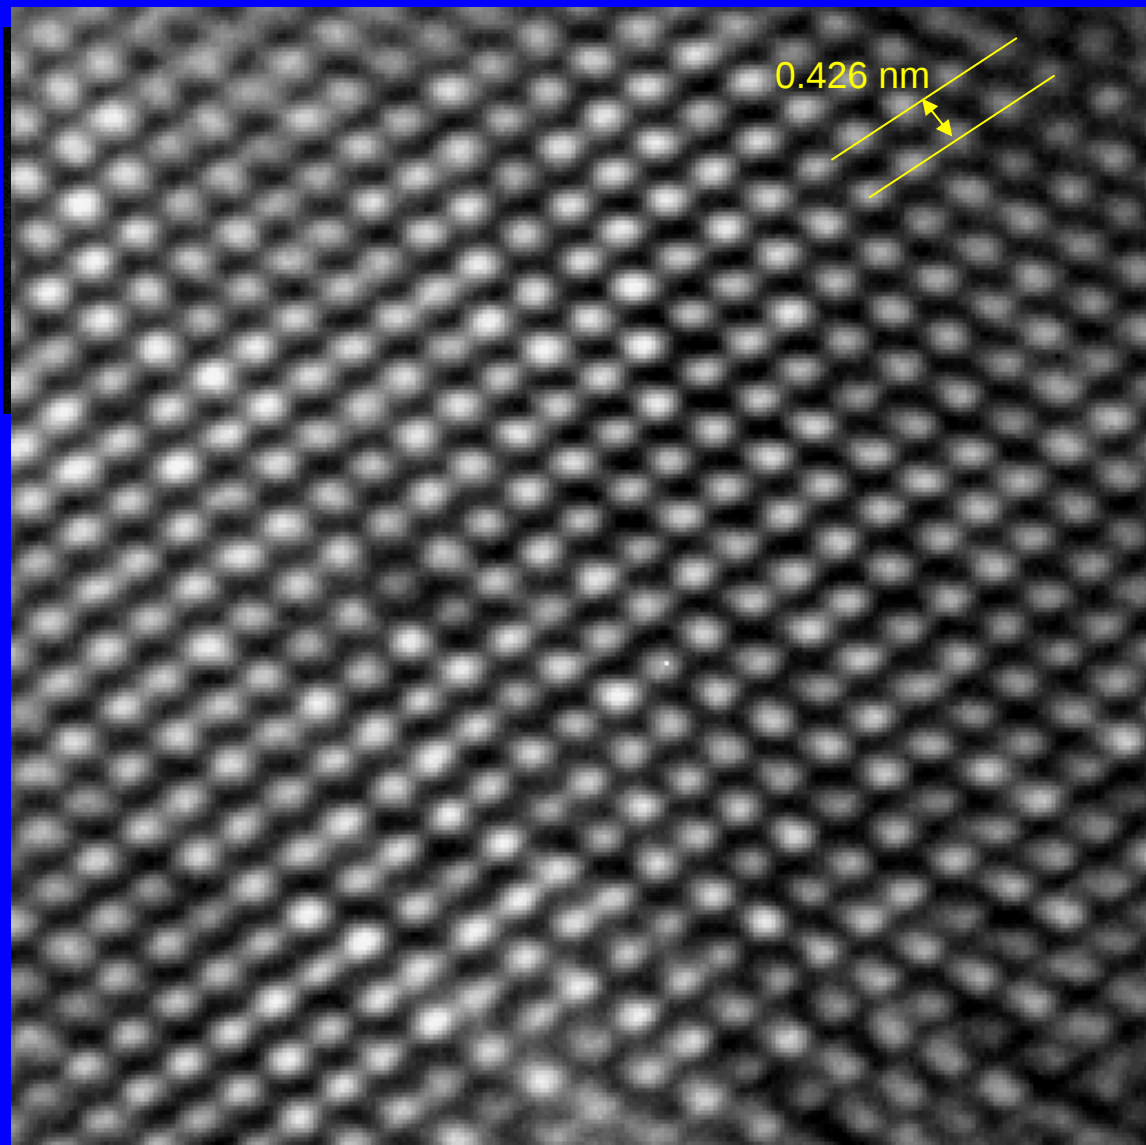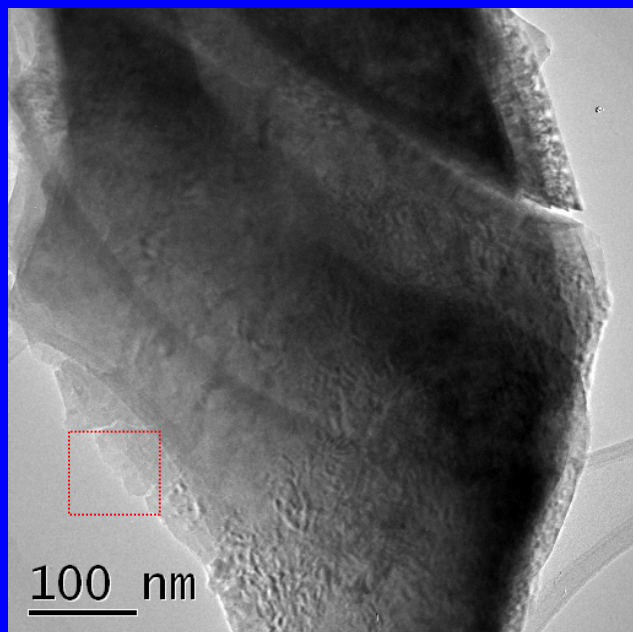

Spot#	d-spacing (nm)
1	0.426
2	0.233
3	0.201
4	0.190

TEM Analysis-bulk

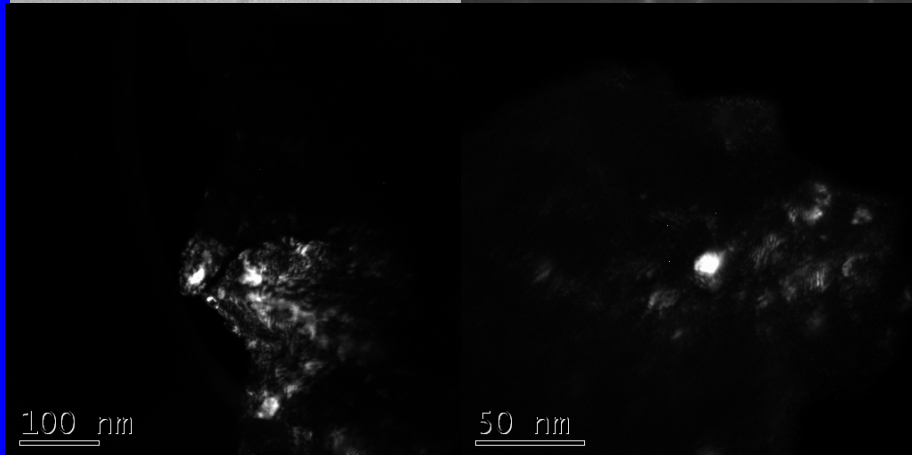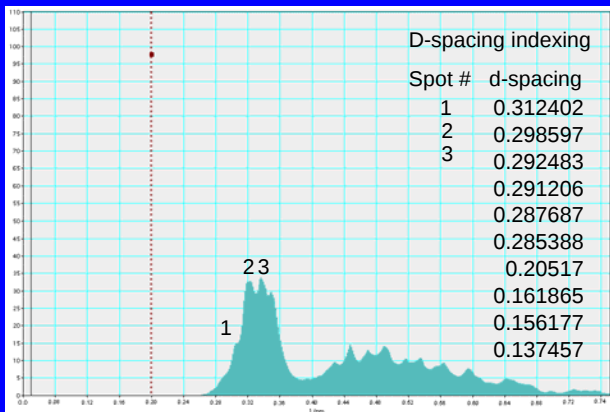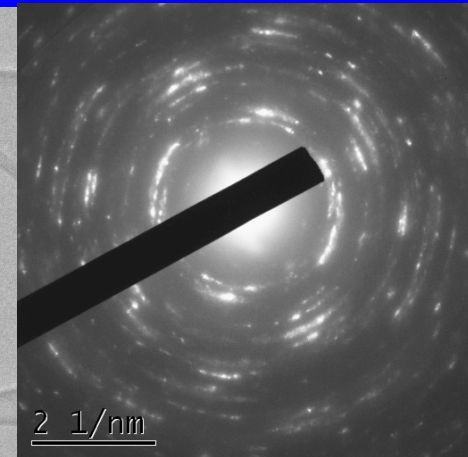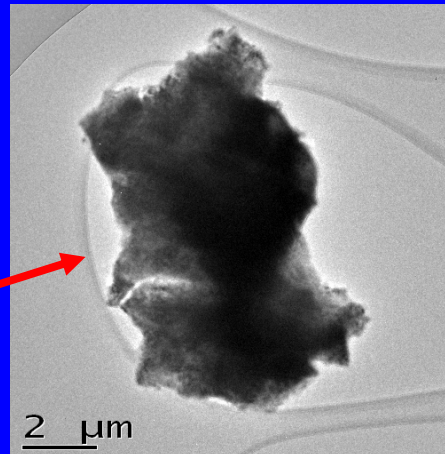

50 nm




- TEM analysis confirms crystallite size < 50 nm
- Diffraction analysis confirms the presence of monoclinic phase

TEM Analysis-bulk

Monoclinic
structure (c2/m)



Nano domains

Some defects
(discontinuity in
the lattice
fringes)

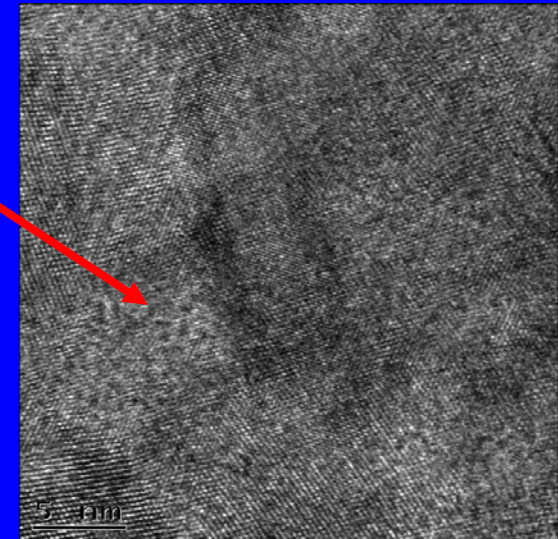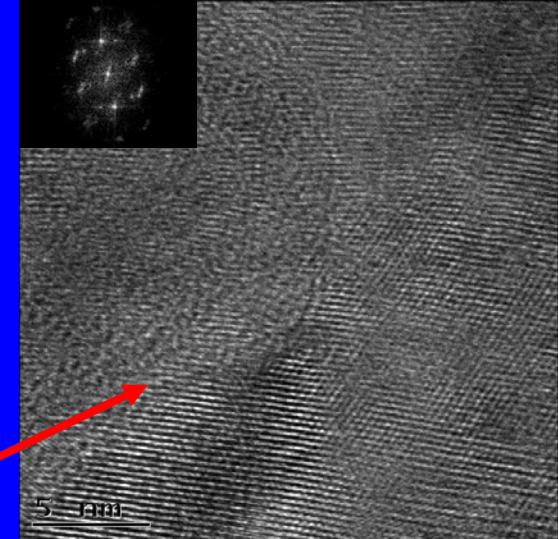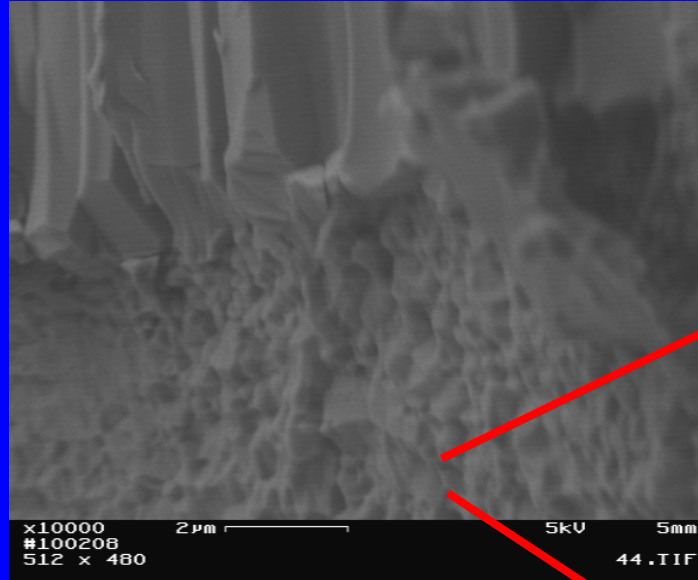


Measured d-spacings from FFT pattern (nm)	(hkl) Monoclinic,C2/m
0.319	(111)
0.292	(401)
0.289	(003)
0.267	(11-2)

columnar grains thinning via wedging process (tripod technique)



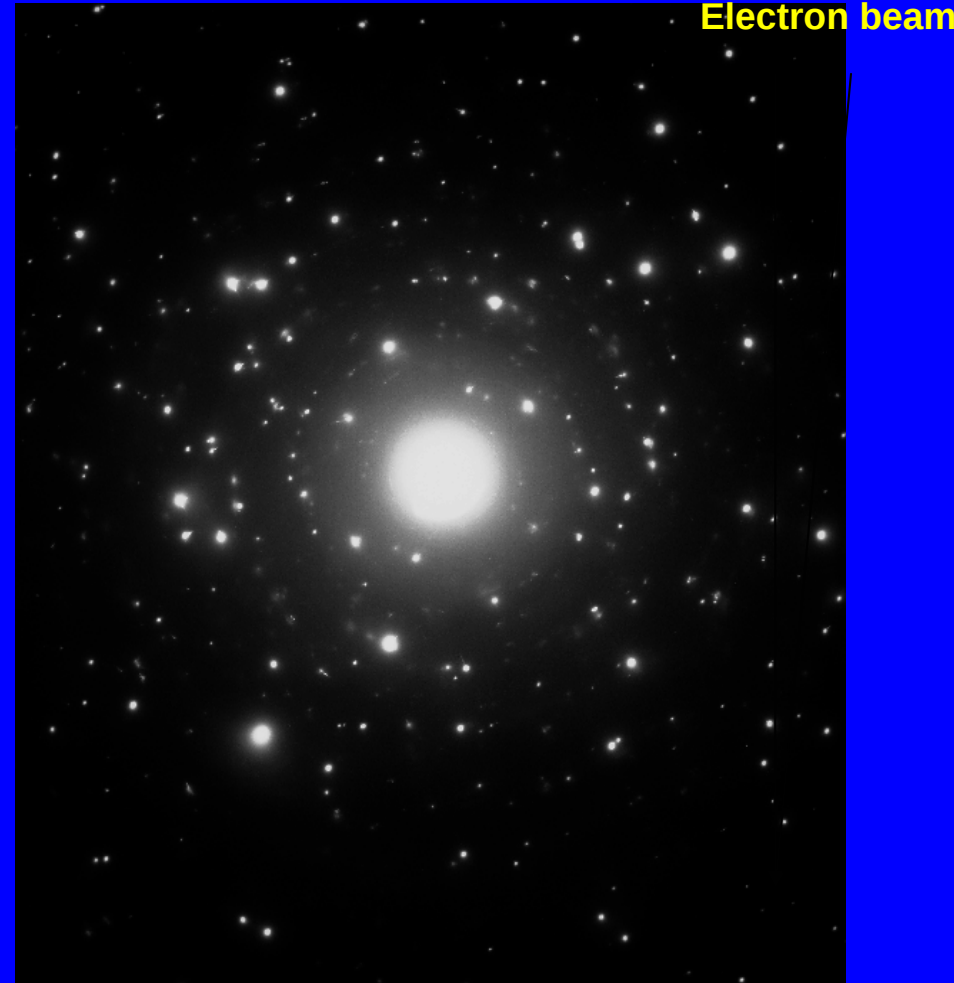
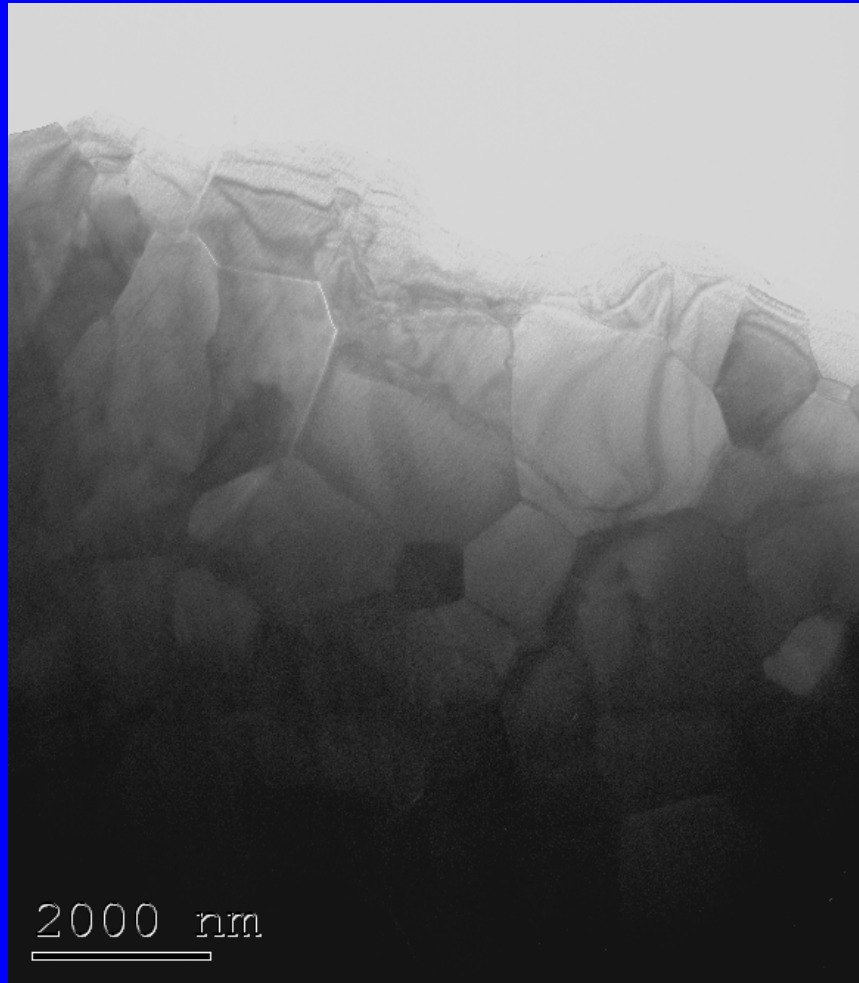


Selected Area electron diffraction analysis

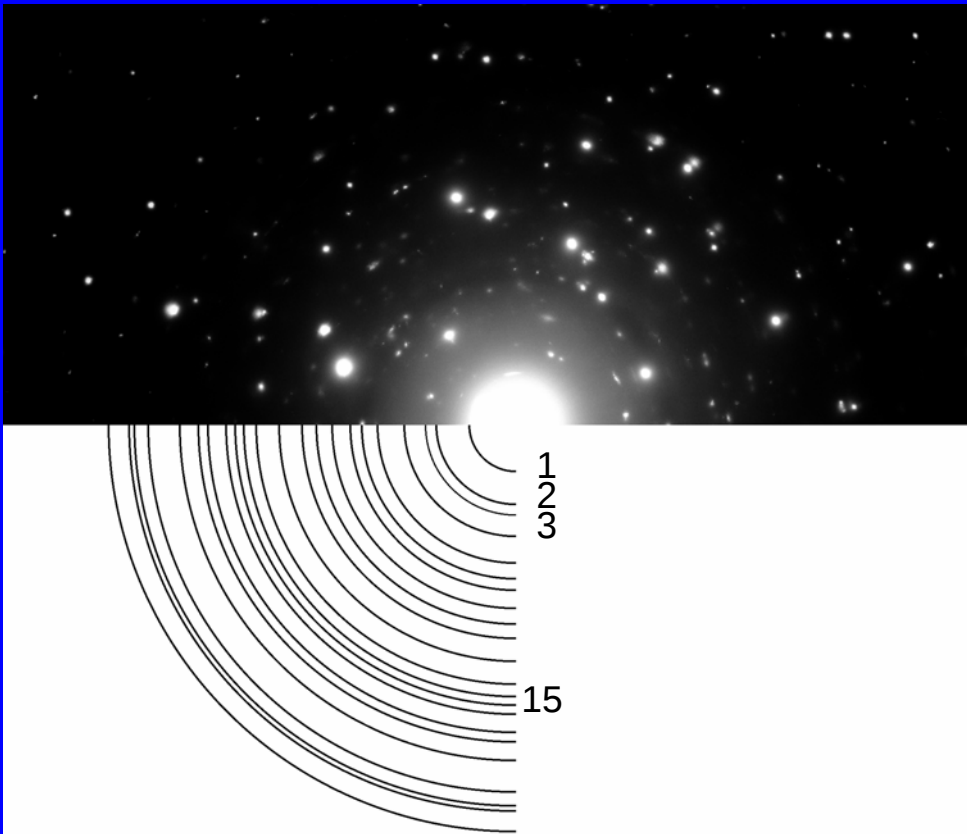

Spot#	d-spacing (nm)	(hkl)
1	0.431	211
2	0.381	220
3	0.308	222
4	0.248	411
5	0.223	332
6	0.208	134
7	0.187	440
8	0.172	611
9	0.161	145
10	0.145	046
11	0.132	800
12	0.126	653
13	0.122	831
14	0.119	752
15	0.112	664

HRTEM analysis of columnar grains

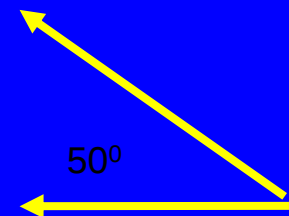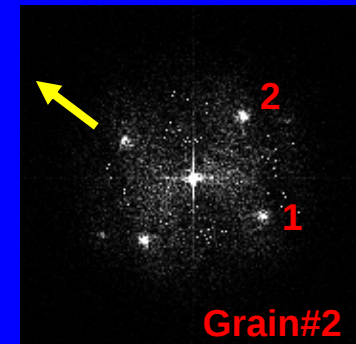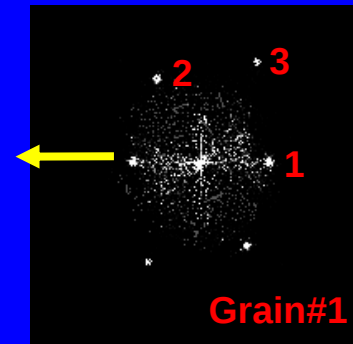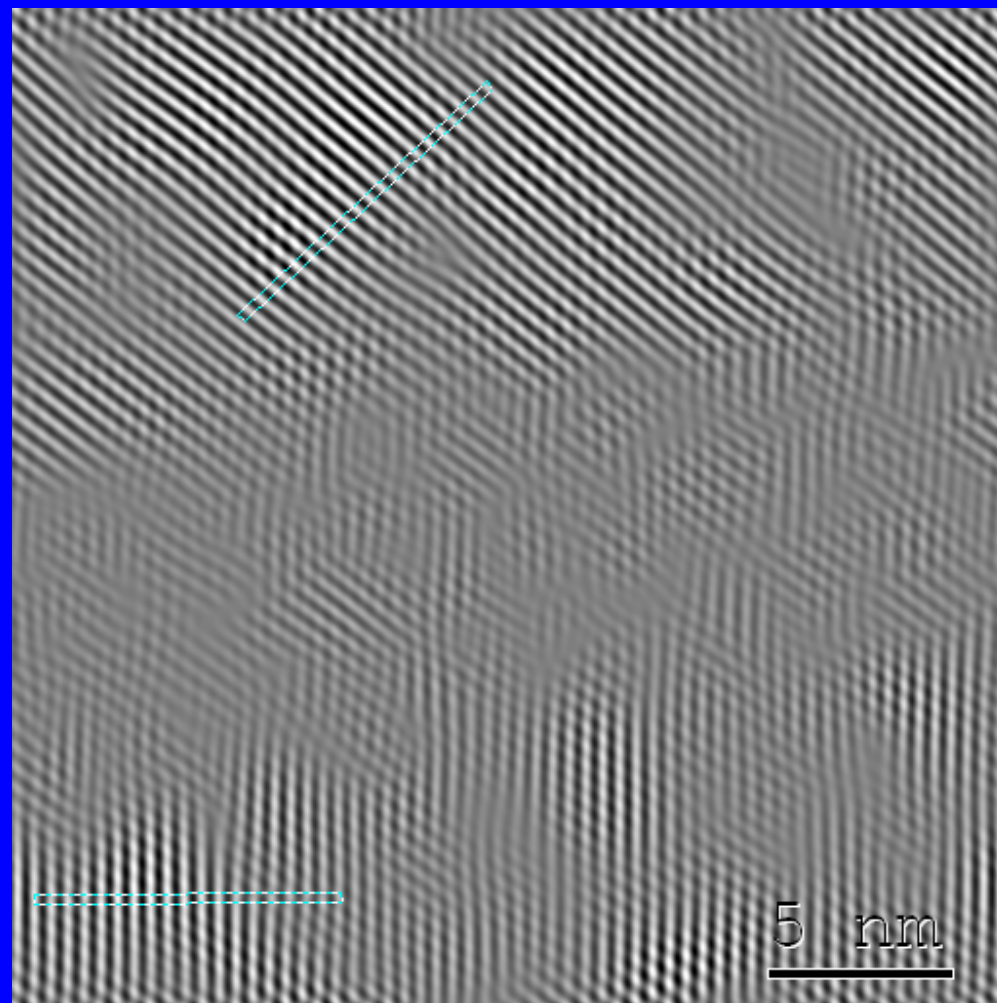



Spot #	d-spacing (nm)	Corresponding plane
Grain#1		
1	0.429	211
2	0.307	222
3	0.254	400
Grain#2		
1	0.428	211
2	0.433	$2\bar{1}\bar{1}$

ZA=0-11

ZA=0-11


HRTEM analysis

Grain #1

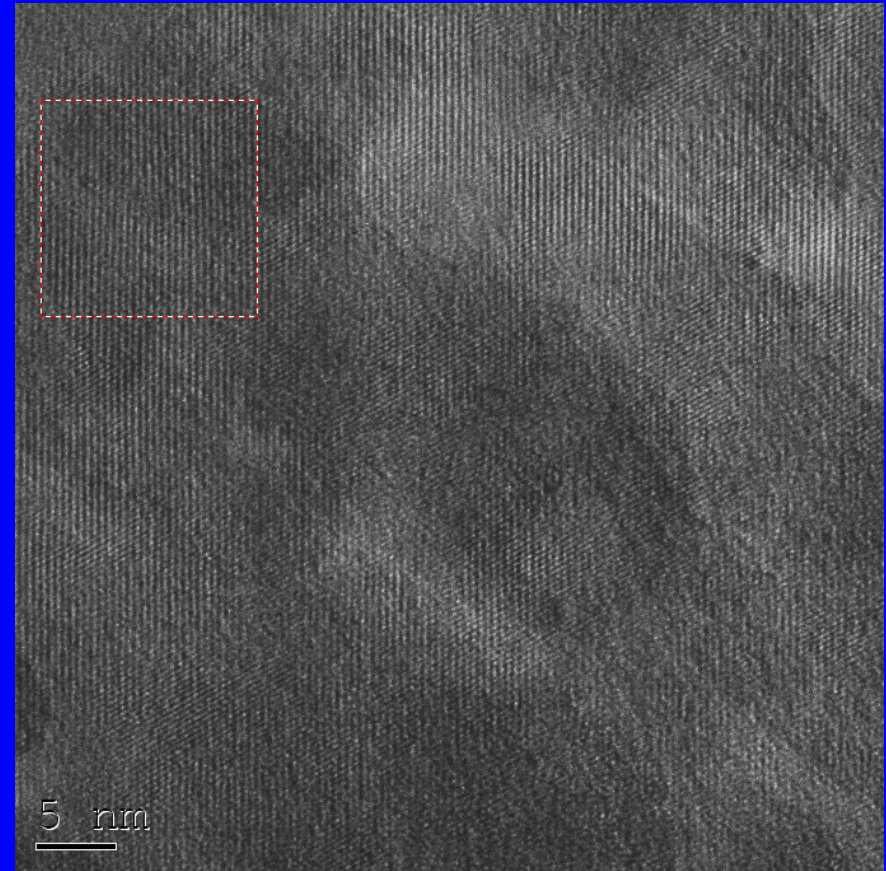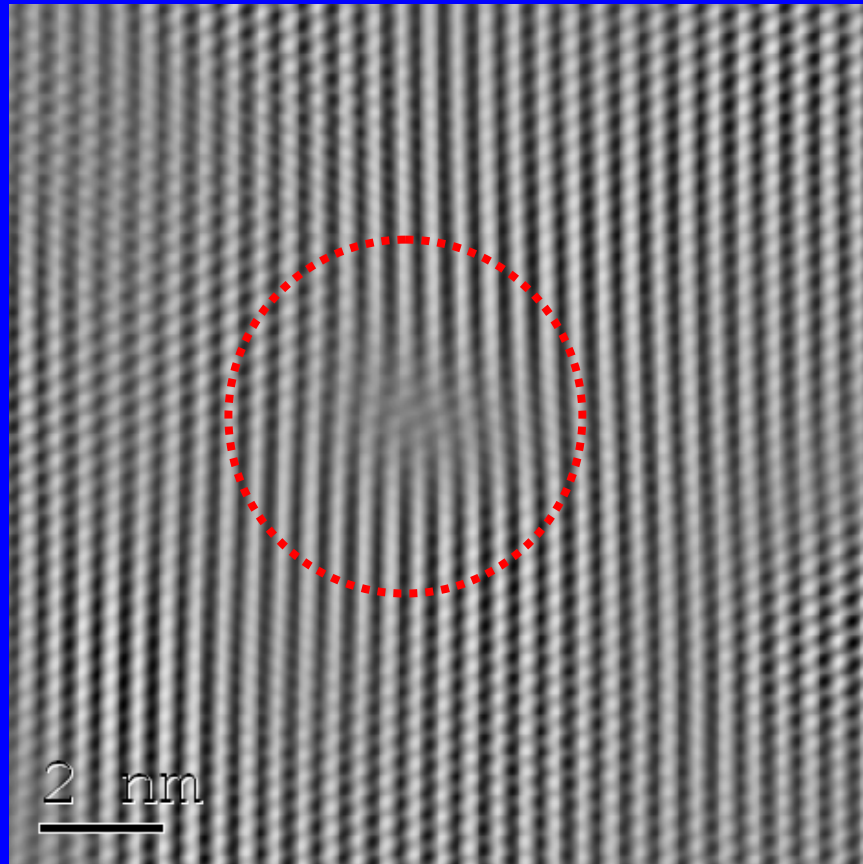




Edge dislocation

Interaction between two dislocations

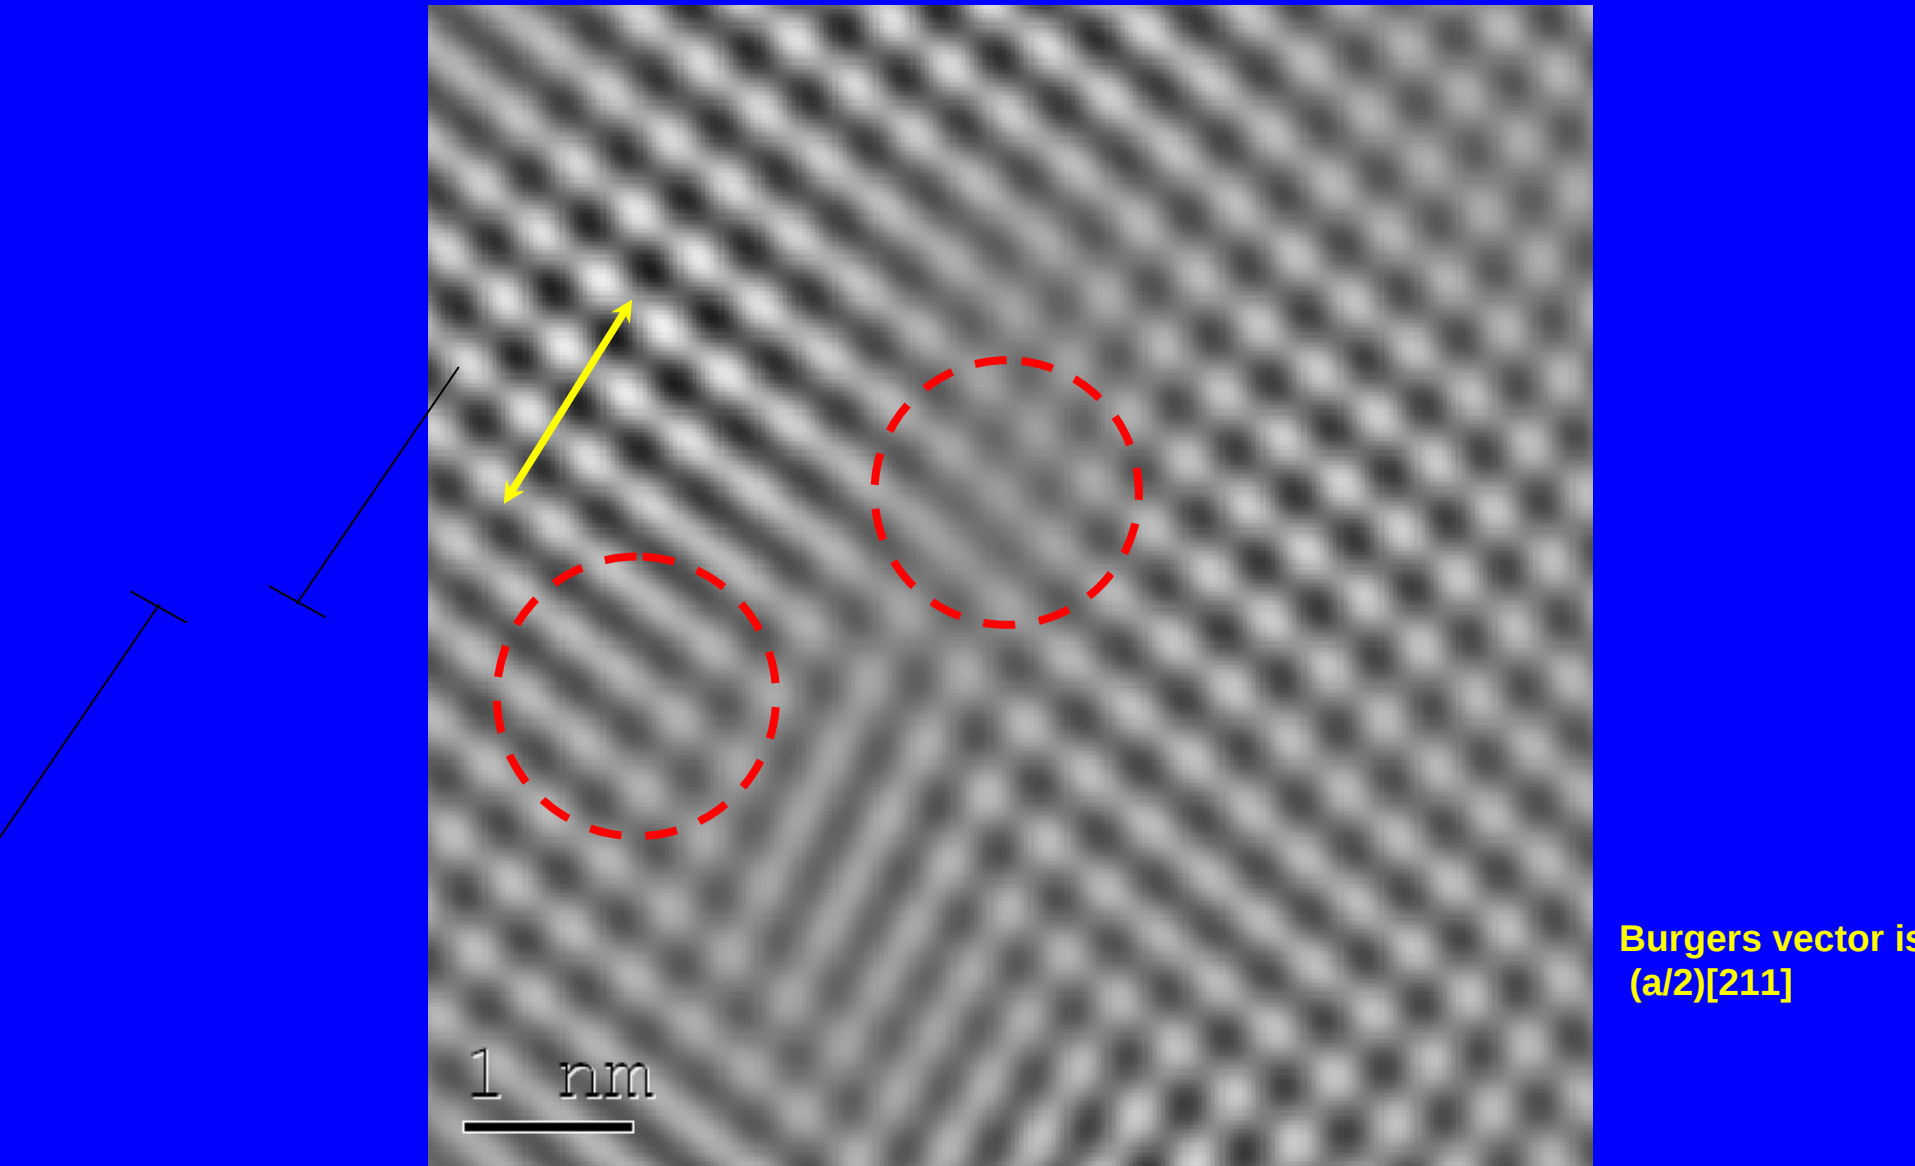

An edge dislocation dipole (positive and negative pair) is separated by three lattice planes 15

Strain mapping from HRTEM

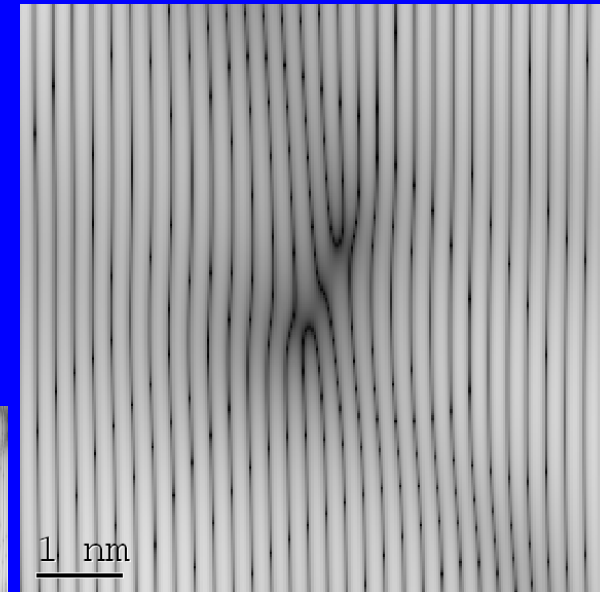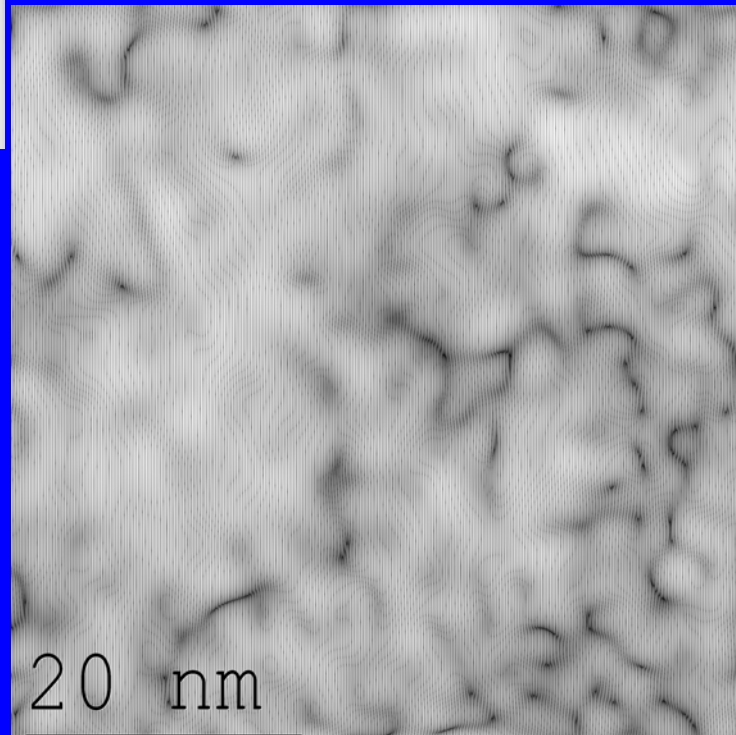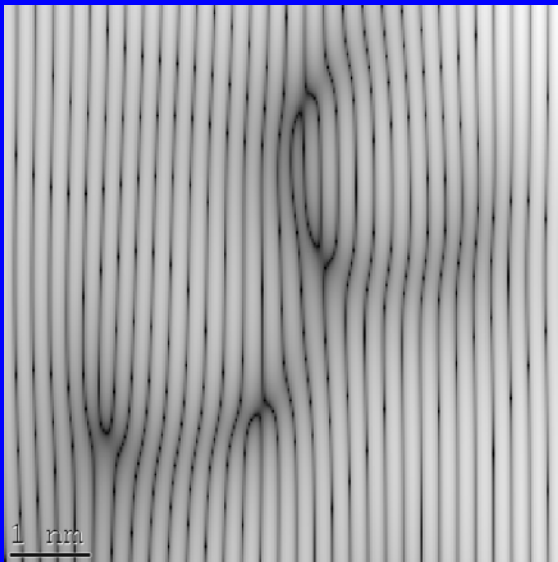

Summary-Conclusions-Future work



- **A new oxygen-deficient columnar grains surface phase has been observed, due to reaction of the graphite crucible with the Y_2O_3 sample**
- **Such reductive decomposition is a promising technique for surface modification of ceramic materials**
- **Experiments to reverse the transformation are under way**
- **This technique will be investigated for other oxide phases**



Acknowledgments

Support for this work from ONR and DARPA is gratefully acknowledged



Artichoke


Artichoke-like tungsten oxide nano particles

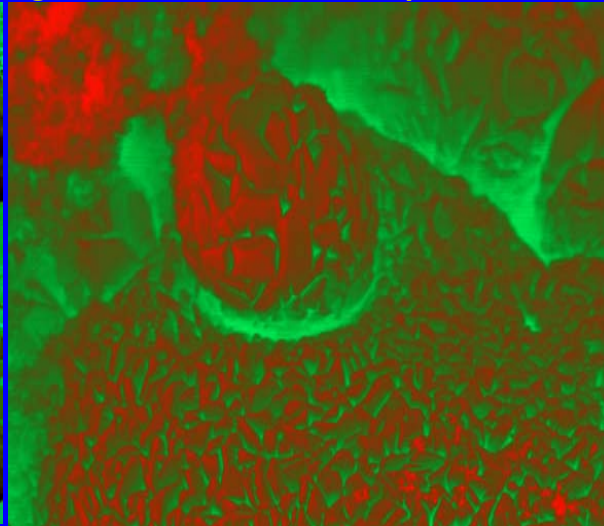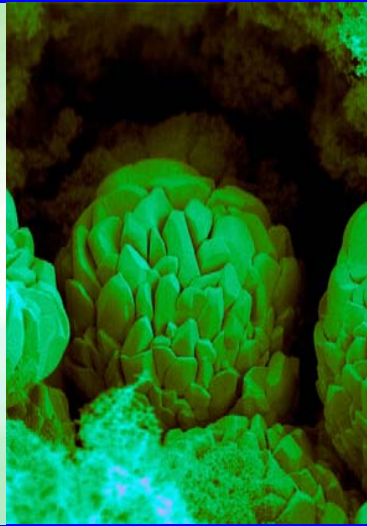



Angles on the point of a pin

Courtesy of John Goodyear

SEM by Jafar F. Al-Sharab

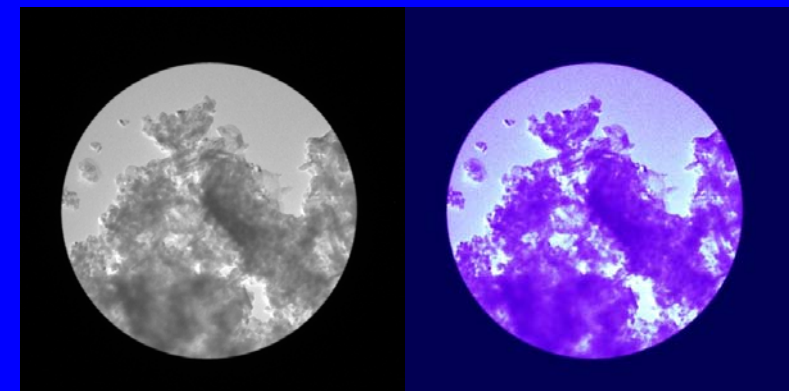

Magnesia-ytria nano particles with selected area aperture shadow

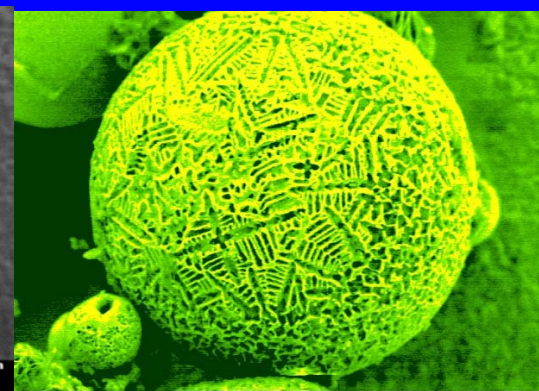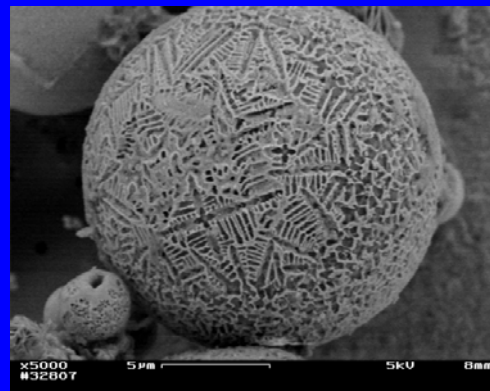

Plasma sprayed magnesia-ytria particles

thank you