

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE (DD-MM-YYYY) 21-10-2010		2. REPORT TYPE Technical Paper		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Functional Perfluoroalkyl Polyhedral Oligomeric Silsesquioxane (F-POSS): Building Blocks for Low Surface Energy Materials				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Joseph M. Mabry (AFRL/RZSM); Yvonne Diaz, Sean M. Ramirez, Timothy S. Haddad (ERC)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER 23030521	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Air Force Research Laboratory (AFMC) AFRL/RZSM 9 Antares Road Edwards AFB CA 93524-7401				8. PERFORMING ORGANIZATION REPORT NUMBER AFRL-RZ-ED-TP-2010-440	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Research Laboratory (AFMC) AFRL/RZS 5 Pollux Drive Edwards AFB CA 93524-70448				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S NUMBER(S) AFRL-RZ-ED-TP-2010-440	
12. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution unlimited (PA #10532).					
13. SUPPLEMENTARY NOTES For presentation at the American Chemical Society Spring 2011 National Conference, Anaheim, CA, 37-31 Mar 2011; for publication in Polymer Preprints.					
14. ABSTRACT Fluorinated polyhedral oligomeric silsesquioxanes (F-POSS), a subclass of POSS, were recently synthesized and have proven to be an excellent low-surface energy material for superhydrophobic and oleophobic surfaces. These F-POSS compounds consist of a silicon-oxide core with a periphery of long chain fluorinated alkyl groups ranging from 6-12 carbon atoms in length. Herein, a disilanol perfluoroalkyl polyhedral oligomeric silsesquioxane (F-POSS-(OH) ₂) has been synthesized via a viable multi-step synthesis (52% yield). These incompletely condensed structures were readily reacted with a variety of dichlorosilanes to produce functional F-POSS structures. Structures were confirmed with multinuclear NMR (¹ H, ¹³ C, and ²⁹ Si) and found to possess different solubility properties compared to the closed-cage F-POSS. These novel structures can be used as the initial building blocks for the development of new superhydrophobic and oleophobic materials.					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT SAR	18. NUMBER OF PAGES 4	19a. NAME OF RESPONSIBLE PERSON Dr. Joseph M. Mabry
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (include area code) N/A

**FUNCTIONAL PERFLUOROALKYL
POLYHEDRAL OLIGOMERIC
SILSESQUIOXANES (F-POSS): BUILDING
BLOCKS FOR LOW SURFACE ENERGY
MATERIALS**

Sean M. Ramirez, Yvonne Diaz, Timothy S. Haddad, and Joseph M. Mabry

Fluorinated polyhedral oligomeric silsesquioxanes (F-POSS), a subclass of POSS, were recently synthesized and have proven to be an excellent low-surface energy material for superhydrophobic and oleophobic surfaces. These F-POSS compounds consist of a silicon-oxide core with a periphery of long chain fluorinated alkyl groups ranging from 6-12 carbon atoms in length. Herein, a disilanol perfluoroalkyl polyhedral oligomeric silsesquioxane (F-POSS-(OH)₂) has been synthesized *via* a viable multi-step synthesis (52% yield). These incompletely condensed structures were readily reacted with a variety of dichlorosilanes to produce functional F-POSS structures. Structures were confirmed with multinuclear NMR (¹H, ¹³C, and ²⁹Si) and found to possess different solubility properties compared to the closed-cage F-POSS. These novel structures can be used as the initial building blocks for the development of new superhydrophobic and oleophobic materials.

FUNCTIONAL PERFLUOROALKYL POLYHEDRAL OLIGOMERIC SILSESQUIOXANES (F-POSS): BUILDING BLOCKS FOR LOW SURFACE ENERGY MATERIALS

Sean M. Ramirez,¹ Yvonne Diaz,² Timothy S. Haddad,¹ and Joseph M. Mabry²

¹ERC Inc., Air Force Research Laboratory Space & Missile Propulsion Division, Edwards Air Force Base, CA 93524-7680

²Air Force Research Laboratory, Space & Missile Propulsion Division, Edwards Air Force Base, CA 93524-7680

Introduction

Polyhedral oligomeric silsesquioxanes (POSS), and their derivatives, have received much interest as a class of robust nanometer-sized building blocks for the development of high performance materials.¹⁻² A fluorinated sub-class, consisting of a series of long-chain fluorinated polyhedral oligomeric silsesquioxane (F-POSS) compounds has recently been developed.³⁻⁵ These F-POSS compounds consist of a silicon-oxide core with a periphery of long chain fluorinated alkyl groups ranging from 6-12 carbon atoms in length. These compounds have proven to be useful in the development and creation of low-surface energy materials.⁶⁻⁹ Currently F-POSS is a standalone compound without any reactive chemical functionality. To circumvent the inert nature of these compounds, research has been performed on the functionalization of the (trifluoropropyl)₇Si₈O₉(OH)₂ with other long chain fluorinated compounds to produce low surface energy materials.¹ Although this synthetic strategy was successful, it was limited by the short length of the trifluoropropyl groups on the trisilanol. To date, there has been no viable synthetic strategy for functionalizable long-chain silanol F-POSS compounds.

Herein, using a similar synthetic strategy to that developed by Feher and coworkers, we report a procedure to synthesize incompletely condensed F-POSS cages.¹⁰ A disilanol perfluoroalkyl polyhedral oligomeric silsesquioxane (F-POSS-(OH)₂) and its subsequent derivatives have been produced. This work represents the first functionalized long-chain F-POSS; these materials find applications in superhydrophobic/oleophobic coatings and low-surface energy materials.

Experimental

Materials. F-POSS (1) was synthesized using previously reported procedures.⁵ All dichlorosilanes were purchased from Gelest and used without further purification unless otherwise noted. All reactions were performed under a nitrogen atmosphere unless otherwise noted.

Instrumentation. ¹H, ¹³C, and ²⁹Si NMR spectra were obtained on a Bruker 300-MHz or 400-MHz spectrometer. A heteronuclear inverse gated decoupling pulse sequence (NOE) with a 12 sec delay was used to acquire ²⁹Si NMR spectra.


Synthesis of (CF₃(CF₂)₇CH₂CH₂)₈Si₈O₁₁(OH)₂ (2). Synthesis of compound 2 will be discussed in detail in future publications (52%). ²⁹Si{¹H} NMR (C₆F₆, 300 MHz) δ -59.2, -65.0, -68.2 (1:1:2). Anal. Calcd. for C₈₀H₃₄F₁₃₆O₁₃Si₈ (found): C, 23.94 (23.99), H, 0.85 (0.75), F, 64.44 (64.72).

General Synthesis of Functional F-POSS Compounds. (CF₃(CF₂)₇CH₂CH₂)₈Si₈O₁₁(O₂Si((CH₂)₇CH₃)₂) (3). A solution of (3.0 g, 0.74 mmol), (2) di-*n*-octadichlorosilane (0.255 g, 0.74 mmol) and NEt₃ (0.1 mL, 1.48 mmol) was stirred for 1 hour. During this time a white precipitate formed. This solution was filtered and poured into ethyl acetate, at which time, a white solid precipitated (1). This solid was removed via filtration and the filtrate was concentrated, then dissolved in diethyl ether and filtered. The filtrate was collected and cooled to 0 °C affording a white precipitate. The precipitate was collected and dried under vacuum to afford a white solid (3) (1.4 g, 44%). ¹H NMR (300 MHz, (CD₃CD₂)₂O, ppm) δ 2.24 (16H), 1.56-1.20 (32H), 5.87 1.15-1.5 (18H) ²⁹Si{¹H} NMR (400 MHz, (CD₃CD₂)₂O, ppm) δ -17.8, -65.4, -68.2, -69.0 (1:2:4:2).

Results and Discussion


Synthesis of (CF₃(CF₂)₇CH₂CH₂)₈Si₈O₁₁(OH)₂. A multi-step reaction procedure was developed to convert the closed-cage F-POSS (1) to an incompletely condensed silsesquioxane structure (2). The first of these steps involves opening a single edge of the POSS structure with strong acid. The

open edge is subsequently converted to a disilanol (ca. 52%) via a sulfate bridge and aqueous work-up. The main side product from each of these steps is compound 1. Elemental analysis and ²⁹Si NMR were used to confirm the structure of 2. The ²⁹Si NMR for compound 2 (-59.2, -65.0, -68.2) displayed a ²⁹Si chemical shift ratio of 1:1:2, which can be attributed to the C_{2v} symmetry of the silsesquioxane (Figure 1). The peak at -58.7 is attributed to the silanols on the POSS structure. This provided evidence for an open cage structure.

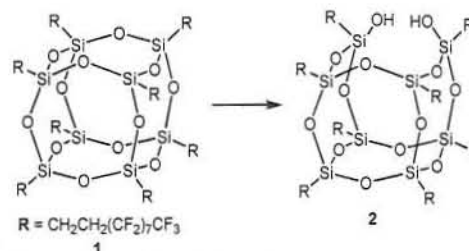

Scheme 1. Synthesis of disilanol F-POSS.

Synthesis of (CF₃(CF₂)₇CH₂CH₂)₈Si₈O₁₁(O₂Si(R₁)(R₂)). The incompletely condensed silsesquioxane (2) can be readily reacted with a variety of dichlorosilanes (Scheme 2). The reaction of 2 with di-*n*-octadichlorosilane in the presence of triethylamine produced compound 3 (ca. 44%). The main side product isolated during reaction was the initial starting material 1. Multinuclear NMR (¹H, ²⁹Si) was used to confirm the structure of 3. The ²⁹Si peaks were at -17.8, -65.4, -68.2, and -69.0, with a ratio of 1:2:4:2 (Figure 1). The peak at -17.8 ppm can be attributed to the Si with the dioctyl group attached. To demonstrate the robustness of the edge closing reaction other dichlorosilanes were reacted with 2 to produce compounds 4-5. Dichlorosilanes with alkyl and aromatic groups were chosen to evaluate the chemical robustness of 2. All of these compounds were confirmed with multinuclear NMR (¹H, ²⁹Si).

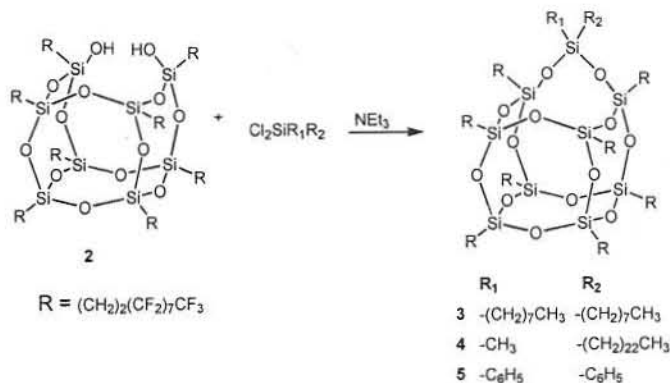

Scheme 2. Synthesis of functionalized F-POSS.

Solubility of (CF₃(CF₂)₇CH₂CH₂)₈Si₈O₁₁(O₂Si(R₁)(R₂)) compounds. Although the large amount of fluorinated alkyl chains on 1 result in desirable properties and low surface energy, this also restricts the solvent choice for 1 to fluorinated solvents. Interestingly, once a non-fluorinated segment is added to an edge of F-POSS, the solubility properties of F-POSS change dramatically. For example, the long hydrocarbon chains present in compound 3 and 4 expand the F-POSS solubility to non-fluorinated solvents such as diethyl ether. Compound 4 demonstrated that unsymmetrical dichlorosilanes could easily be attached to a POSS cage. The long flexible chains for these molecules aided in rendering F-POSS soluble in non-fluorinated solvents. However groups such as a phenyl (8) were not able to improve the solubility of F-POSS. This can be attributed to the stiffness of the two phenyl groups on the POSS cage. We are currently developing other modified F-POSS structures.

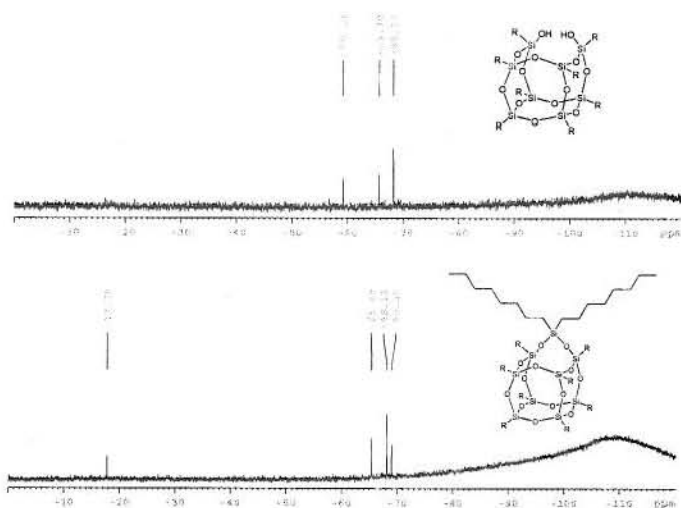


Figure 1. ^{29}Si NMR of 2 (top), and 3 (bottom).

Conclusions

The synthesis of disilanol F-POSS from F-POSS was accomplished in a three step reaction process. This incompletely condensed POSS structure was demonstrated to be reactive towards dichlorosilanes to produce a variety of functional F-POSS structures. These novel structures can be used as the initial building blocks for the development of new superhydrophobic and oleophobic materials.

Acknowledgements. The authors would like to thank the Air Force Office of Scientific Research the Air Force Research Laboratory Propulsion Directorate for financial support.

References

- (1) Cordes, D. B.; Lickiss, P. D.; Rataboul, F. *Chem. Rev.* **2010**, *110*, 2081.
- (2) Phillips, S. H.; Haddad, T. S.; Tomczak, S. J. *Curr. Opin. Solid State Mater. Sci.* **2004**, *8*, 21.
- (3) Iacono, S. T.; Budy, S. M.; Mabry, J. M.; Smith, D. W., Jr. *Macromolecules* **2007**, *40*, 9517.
- (4) Iacono, S. T.; Vij, A.; Grabow, W.; Smith, D. W., Jr.; Mabry, J. M. *Chem. Commun.* **2007**, 4992.
- (5) Mabry, J. M.; Vij, A.; Iacono, S. T.; Viers, b. D. *Angew. Chem., Int. Ed.* **2008**, *47*, 4137.
- (6) Anderson, S. E.; Bodzin, D. J.; Haddad, T. S.; Boatz, J. A.; Mabry, J. M.; Mitchell, C.; Bowers, M. T. *Chem. Mater.* **2008**, *20*, 4299.
- (7) Choi, W.; Tuteja, A.; Chhatre, S.; Mabry, J. M.; Cohen, R. E.; McKinley, G. H. *Adv. Mater.* **2009**, *21*, 2190.
- (8) Tuteja, A.; Choi, W.; Ma, M.; Mabry, J. M.; Mazzella, S. A.; Rutledge, G. C.; McKinley, G. H.; Cohen, R. E. *Science* **2007**, *318*, 1618.
- (9) Tuteja, A.; Choi, W.; Mabry, J. M.; McKinely, G. H.; Cohen, R. E. *Proc. Natl. Acad. Sci. U. S. A.* **2008**, *105*, 18200.
- (10) Feher, F. J.; Soulivong, D.; Nguyen, F.; Ziller, J. W. *Angew. Chem., Int. Ed.* **1998**, *37*, 2663.