

Robustly Single-mode Polarization Maintaining Er/Yb co-doped LMA Fiber for High Power Applications

A. Carter, J. Farroni, K. Tankala, B. Samson, D. Machewirth and N. Jacobson

Nufern, 7 Airport Park Road, East Granby, CT 06026
Phone: (860)408-5000; fax: (860)408-5080; e-mail: acarter@nufern.com

W. Torruellas and Y. Chen

Fibertek Inc., 510 Herndon Parkway, Herndon, VA 20170

M-Y. Cheng and A. Galvanauskas

EECS Department, University of Michigan, 1301 Beal Avenue, Ann Arbor, MI 48109

A. Sanchez

AFRL/DELO, Kirtland AFB, Albuquerque, NM

Abstract: We demonstrate a large core diameter PM Er/Yb fiber incorporating a unique raised inner-cladding which facilitates the use of conventional LMA mode selection techniques to achieve robustly single-mode operation, making it ideally suited to high power applications.

© 2007 Optical Society of America

OCIS codes: (060.2280) Fiber design and fabrication; (060.2320) Fiber optics amplifiers and oscillators

1. Introduction.

The development of large-mode area (LMA) fibers has lead to demonstrations of kiloWatt level CW outputs and megaWatt level peak powers in sub-nanosecond pulsed amplifiers. Such output powers have been achieved with near diffraction-limited output beam quality, because the low NA core supports only a few modes and the higher order modes can be easily discriminated against by preferential seeding [1], and/or bending [2]. However, due to the inherent difficulties associated with manufacturing fibers containing the relatively high lanthanide ion dopant concentrations required for high optical-efficiency whilst maintaining a low core NA, the development of LMA fibers has largely been restricted to ytterbium fibers for use at around $1.0\mu\text{m}$. In spite of the numerous advantages, a significant drawback of the ytterbium based system is the relatively high sensitivity of the human eye to wavelengths in the $1.0\mu\text{m}$ region. Consequently for certain applications, such as ranging, pollution monitoring, clear-air turbulence analysis and free-space communications, operating in the “eye-safe” $1.5\text{--}2.0\mu\text{m}$ range is preferred.

Notwithstanding the lack of LMA fibers, a number of significant steps toward the extraction of high output powers from multimode Er/Yb fibers have been reported. Koroshetz *et. al.* [3], demonstrated a 40W, 10Gb/s amplifier; Shen *et. al.* [4] reported 188W of CW output with an M^2 of 1.9 using fibre with a $30\mu\text{m}$ 0.22NA core; and Yusimet. *al.* [5] employed a $20\mu\text{m}$ core fiber, which supports 30 modes, to achieve 100W output with a near diffraction-limited beam by employing single-mode fiber based components in the cavity and making highly precise splices between the single-mode fibers and the multi-mode active fiber. Although a high-power near diffraction-limited output was achieved, such methods are cumbersome and further emphasize the need for LMA fibers. We recently reported the development of such an LMA fiber [6] and present here an advancement in this technology that allows the fabrication of highly efficient, polarization maintaining (PM) LMA fibers. A PM-LMA Er/Yb co-doped fiber suitable for nanosecond pulsed amplification applications as well as high power CW amplification has been designed and fabricated. This fiber possesses a relatively large $25\mu\text{m}$ core and $300\mu\text{m}$ cladding diameter but incorporates a unique raised inner cladding (pedestal) which reduces the V-value at 1550nm to less than 5, thereby facilitating the use of seeding and/or coiling technology to achieve single-mode operation with relative ease. Manufacturing challenges for these novel fibers are discussed and amplification performance data including up to 40% power efficiency is presented.

2. Experiment and results.

The challenges associated with fabricating LMA Er/Yb and Tm-doped fibers have previously been discussed in detail by Tankala *et. al.* [6]. In the case of a PM-LMA fiber the manufacturing is further complicated by the spatial requirements of the stress inducing elements [7] and this is further exacerbated here by the presence of the pedestal. Care is also required so as to avoid shattering the highly stressed core during the machining steps. Notwithstanding these

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 08 MAY 2007		2. REPORT TYPE		3. DATES COVERED 00-00-2007 to 00-00-2007	
4. TITLE AND SUBTITLE Robustly Single-mode Polarization Maintaining Er/Yb co-doped LMA Fiber for High Power Applications				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) AFRL/DELO,Kirtland AFB,Albuquerque,NM,87117				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT We demonstrate a large core diameter PM Er/Yb fiber incorporating a unique raised inner-cladding which facilitates the use of conventional LMA mode selection techniques to achieve robustly single-mode operation, making it ideally suited to high power applications					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 3	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

complications, by careful positioning and compositional optimization of the stress elements we found that it is possible to achieve a birefringence of around $2.0\text{-}2.5 \times 10^{-4}$. We chose a core to pedestal NA of around 0.09 and a pedestal diameter of around 40micron, because at such a diameter the pedestal behaves as a “true” cladding to the core rather than an extended core feature [6]. The fiber was drawn in a double clad (DCF) geometry with a 0.46NA provided by a fluoroacrylate polymer, the peak core absorption of the erbium (circa 1550nm) was 25dB/m and the 915nm cladding absorption was measured to be around 0.8dB/m. The fiber was tested in both CW and nanosecond high pulse energy amplifiers. Depending upon the amplifier configuration and length of fiber used, slope efficiencies of between 30-40% were typical; see Figure 1. Using an EM4 high-power DFB laser to produce 2ns seed pulses with 550pJ pulse energy (at a pulse repetition rate of 10Kpps), amplification of around 50dB (to ~70uJ) was achieved using the PM-LMA-EYDF in the third stage of a three stage amplifier; for an average power of 0.7W. A 30% optical to optical efficiency was also achieved when amplifying 500ns seed pulses (at 50Kpps) to achieve 160μJ/pulse (around 300W peak power), before the onset of SBS.

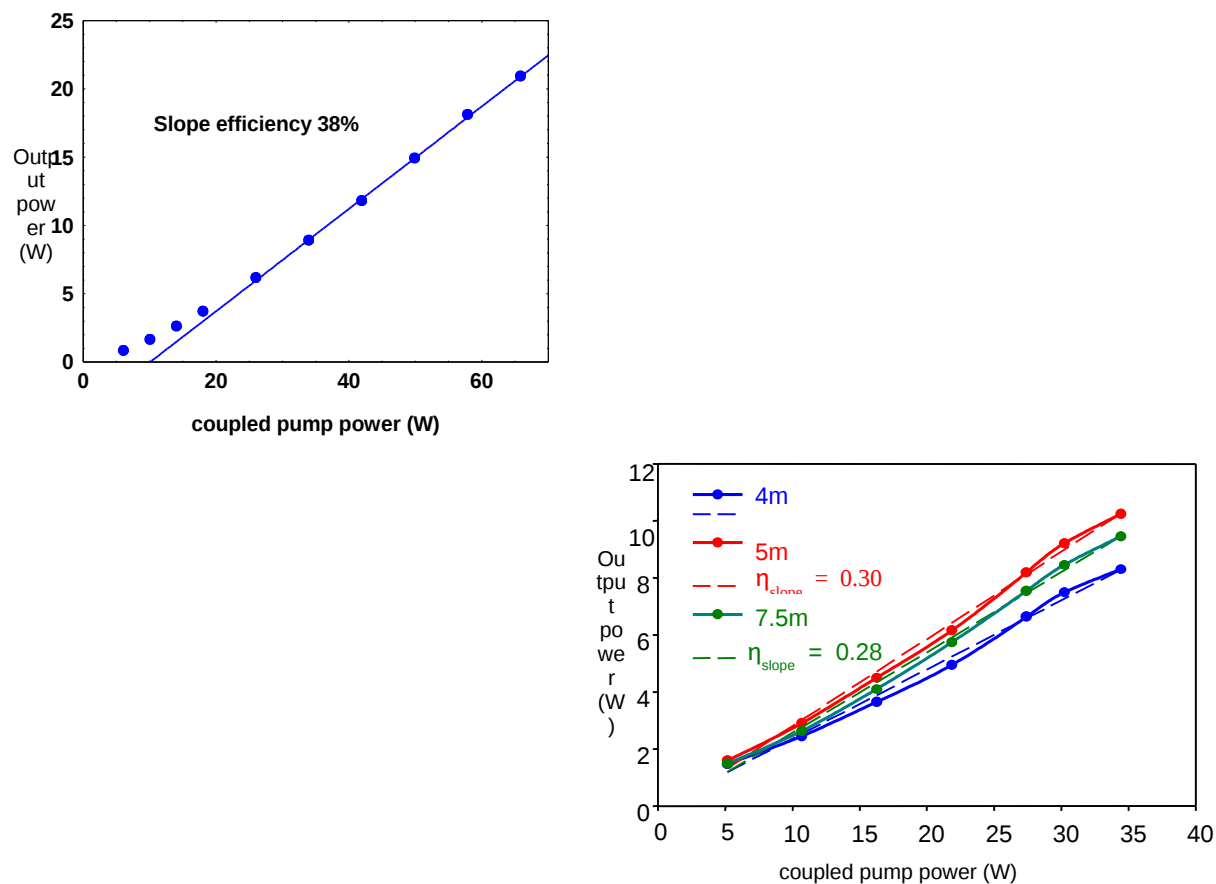


Figure 1: Slope efficiency of a 10m long PM-LMA-EYDF-25/300 CW fiber amplifier pumped at 975nm and seeded with 100mW at 1559nm (left) and Slope efficiency of a 500ns seeded amplifier as a function of coupled pump power for 4m, 5m and 7.5m fiber (right).

We also used standard mode matching techniques, in a seeded amplifier configuration, to compare this LMA fiber with that of a more typical 0.17NA 18μm core fiber and found that despite the larger core single-mode output was more readily achieved from the LMA fiber. We measured the output signal beam after propagating through 10m of Er/Yb amplifier and found that the achievable mode quality was close to diffraction-limited with a measured M^2 of 1.1.

In conclusion, we have found that by incorporating a pedestal feature between the core and cladding of a conventional PM Er/Yb DCF it is possible to create an LMA-like structure and thereby increase the non-linear threshold and achieve the pulse energies, peak powers, efficiency and beam quality suitable for many “eye-safe” coherent monitoring systems.

The authors acknowledge AFRL for funding development of the PLMA Er/Yb fibers (Contract#: FA9451-05-D-0218).

References

- [1] M.E.Fermann, "Single-mode excitation of multimode fibers with ultrashort pulses", Optics Letters, **23**, pp.52-54, 1998.
- [2] J.P.Koplow, D.A.V.Kliner, and L.Goldberg, "Single-mode operation of a coiled multimode fiberamplifier", Optics Letters, **25**, pp.442, 2000.
- [3] J.Koroshetz, I.T.McKinnie, E.Schneider, D.Smith, J.Unternaherer, W.A.Clarkson, J.Nilsson, A.Carter, K.Tankala, J.Farroni, E.A.Watson, B.Stadler and G.Duchak, "High power eye-safe fiber transmitter for free space optical communications", Advanced Solid-State Photonics, **MA2**, Santa Fe, 2004.
- [4] D.Y.Shen, J.K.Sahu and W.A.Clarkson, "Highly efficient Er,Yb-doped fiber laser with 188W free-running and >100W tunable output power", Optics Express, **13(13)**, pp.4916-4921, 2005.
- [5] A.Yusim, J.Barsalou, D.Gapontsev, N.Platonov, O.Shkurikhin, V.Gapontsev, Y.Barannikov and F.Shcherbina, "100 Watt single-mode CW linearly polarized all-fiber format 1.56- μ m laser with suppression of parasitic lasing effects", Proceedings of SPIE Vol. **5709**, pp.69-77, 2005.
- [6] K.Tankala, B.Samson, A.Carter, J.Farroni, D.Machewirth, N.Jacobson, A.Sanchez, A.Galvanauskas, W.Torruellas and Y.Chen, "New Developments in High Power Eye-Safe LMA Fibers", **Invited paper**, Photonics West, **6102-06**, San Jose, USA, January 2006.
- [7] K.Tankala, A.Carter, D.P.Machewirth, J.Farroni, J.Abramczyk and U.H.Manyam, "PM-double clad fibers for high-power lasers and amplifiers", Photonics West, **4974-40**, San Jose, 2003.