

Final Report

Title of project:

Basic Research for AOARD 104092 "Evaluation of laser oscillation property
in wave guide polycrystalline ceramic"

by

Dr. Tomosumi Kamimura

Osaka Institute of Technology,
5-16-1 Ohmiya, Asahi-ku, Osaka 535-8585, Japan

Submitted to

Dr. Kumar Jata, Program Manager

Asian Office of Aerospace Research & Development (AOARD)

7-23-17 Roppongi

Minato-ku, Tokyo 106-0032

TEL:(03)-5410-4409 FAX:(03)-5410-4407

Report Documentation Page			Form Approved OMB No. 0704-0188		
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 21 SEP 2011		2. REPORT TYPE Final		3. DATES COVERED 04-09-2010 to 04-09-2011	
4. TITLE AND SUBTITLE Evaluation of laser oscillation property in wave guide polycrystalline ceramic.			5a. CONTRACT NUMBER FA23861014092		
			5b. GRANT NUMBER		
			5c. PROGRAM ELEMENT NUMBER		
6. AUTHOR(S) Tomosumi Kamimura			5d. PROJECT NUMBER		
			5e. TASK NUMBER		
			5f. WORK UNIT NUMBER		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Osaka Institute of Technology,5-16-1 Ohmiya,Asahi-ku,Osaka,JP,535-8585			8. PERFORMING ORGANIZATION REPORT NUMBER N/A		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) AOARD, UNIT 45002, APO, AP, 96338-5002			10. SPONSOR/MONITOR'S ACRONYM(S) AOARD		
			11. SPONSOR/MONITOR'S REPORT NUMBER(S) AOARD-104092		
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT The laser characteristics of waveguide sample manufactured by World Laboratory Co., Ltd. were evaluated. Maximum output of 120 W was obtained from approximately 264 W of absorbed power. Greater than 50% slope efficiency was achieved?the target of in this effort--without cracking the sample. However, in the region with 264 W or more absorbed power, saturation of the output power occurred. The saturation of this output is thought to be caused by a thermal cooling factor. To obtain higher output power, introducing a high-power sample cooling system is indispensable. Oscillation experiments of still-higher output are planned for a follow-on series of experiments.					
15. SUBJECT TERMS ceramic laser, Laser Physics					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 5	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

1. SUMMARY of PREVIOUS RESULTS

The laser characteristics of waveguide ceramic sample manufactured by Dr. Ikesue of World Laboratory Co., Ltd. were evaluated with grant "Basic Research for AOARD 104045. The waveguide sample of the 32mm length was prepared for the evaluation for the side-pumping excitation. Current maximum output 62W was obtained from approximately 150 W of absorbed powers. Over 50% of slope efficiency was achieved. The crack of the sample and thermal saturation of the output power cannot be confirmed in this experiment. The oscillation experiment of higher output is going to be performed in this grant.

2. TRAGET of RESERCH

Waveguide type laser oscillation

A side-pumping system is used for an oscillation test. Stacked LDs (808nm) of the maximum output 432W is prepared for this purpose.

[Merit of side-pumping system]

- (1) It is suitable for pumping with a long core.
- (2) High efficiency (optical-optical) can be acquired.
- (3) The laser beam of the excellent quality is obtained.

[Sample condition]

(2) Advanced waveguide type using composite core layer

Size: 1.2 x 10 x 32mm

Core doping concentration: 0.6at%

Core thickness: 0.4mm

[Performance goal]

Slope efficiency: over 50%

Beam quality: Good

Budget Summary

Sample Type	Output Power	Pomp	Schedule	Budget
Waveguide/Adv. waveguide	50W		achieved	25k
	100W		Apr.15	

3. EXPERIMENTAL RESULTS

The sample of the 32mm length was prepared for the evaluations of the possibility of the side-pumping (Fig. 1a). All of sample was manufactured by Dr. Ikesue doctor of world laboratory Co., Ltd. A laser active layer (e.g., Nd:YAG with 400 μ m thickness) is arranged at the center, and low refractive index materials (high thermal conductive material: pure YAG) is strongly bonded at the atomic level on both faces of it. Each thickness of pure YAG is over 400 μ m thickness. As a result, the thickness of the whole sample becomes 1.2mm (Fig. 1b). From a micro photography, the interfacial condition bonded together is excellent. In the side of the sample (10mm x 1.2mm), gradient processing (3 degree and 4 degree) is taken for ASE prevention. Sapphire was placed outside them more to make pump beam have total internal reflection (TIR). Power density of the pump beam determined the thickness of YAG and the Nd:YAG.

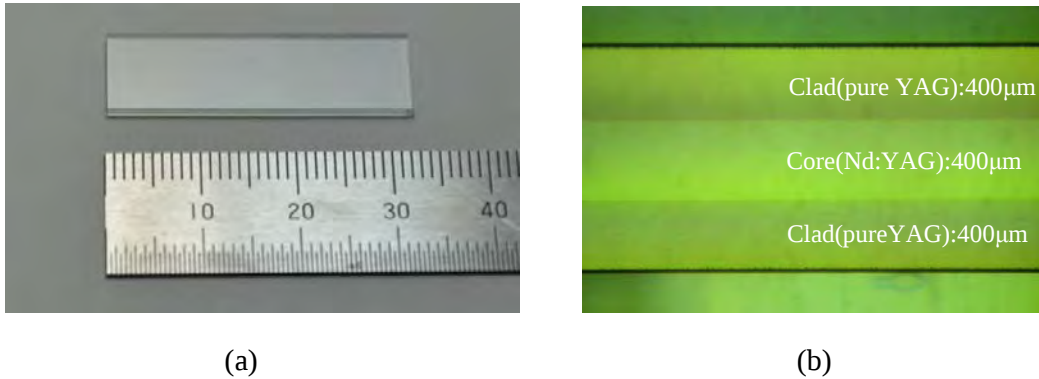


Fig.1(a) Photograph of the sample with 400 μ m thickness core, (b) Micro photography of the bonding boundary surface.

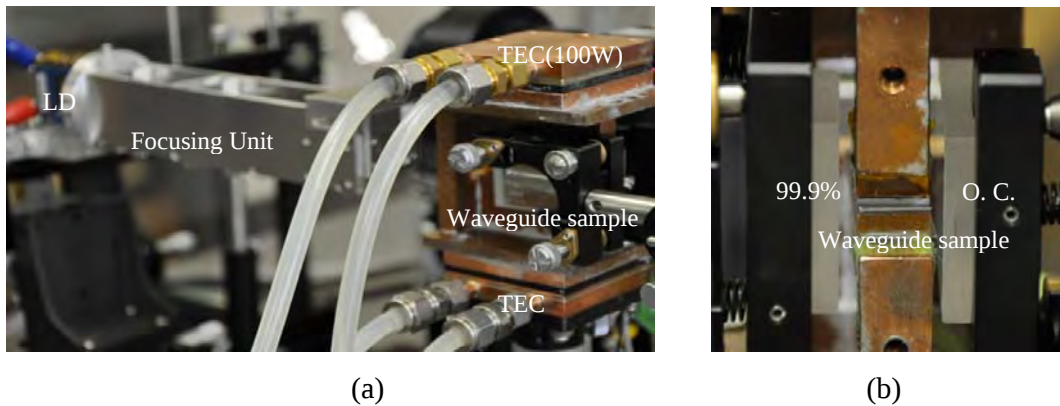


Fig.2(a) Schematic layout of the laser oscillation experiment, (b) Side-view of the sample holder

LD of 808nm was used for a laser oscillation experiment as a pumping laser light. Maximum output of the LDs is 432W. The pumping laser light was incident from edge face of 1.2mmx10mm of the sample. A sample of 32mm propagates as parallel beam by collimating to 8mm width with a focusing unit. A vertical focusing condition was adjustable from 400 μ m to 1000 μ m. The sample was attached in a copper heat sink by using heat conduction grease. The heat sink cooled off in two thermo-electronic cooler (TEC: 100W). AR coating was coated for all the edge face of the sample. The sample was put between two flat mirrors and constituted a resonator. The mirror of 20% of transmittance was selected as an output coupler (O. C.). The resonator length was approximately 13mm. In this condition, input power 10% or more become the transmitted leak power. The most of the output are fixed by length of around 10mm, but the remaining part contributes to output, too.

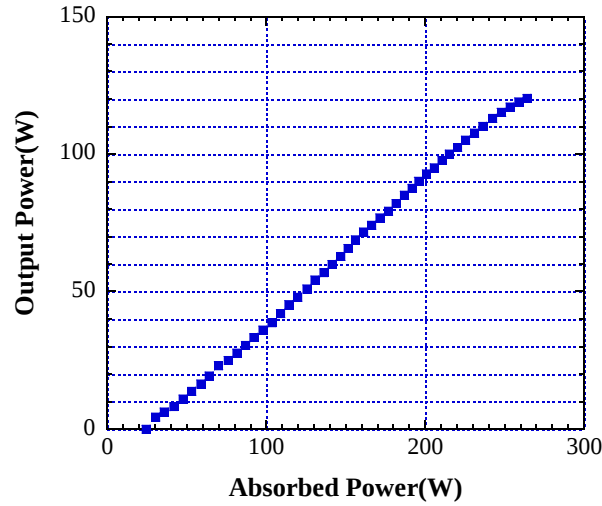


Fig. 3. Relationship between absorbed power and output power for side-pumping experiment.

Relationship between absorbed power and output power is shown in figure 3. The laser output was taken out from the surface of 1.2mm x 32mm. As absorbed powers increased, the laser output rapidly increased. At the region with 80W or more absorbed power, output power almost increases in linear shape. Maximum output 120W was obtained from approximately 264 W of

absorbed powers. Over 50% of slope efficiency was achieved without cracking the sample. However, in the region with 264W or more absorbed power, saturation of the output power occurred. The saturation of this output is thought to be caused by a thermal factor. The balance of occurrence of thermal saturation and the cooling of the heat are as follows. The heat conduction loss from a sample in the sample holder cannot be measured. However, coolability is thought to be just short at the maximum output of 120W. To obtain higher output power, introducing the high-power sample cooling system is indispensable.

Absorbed power (264W) – Output power (120W) > Cooling power (200W) – thermal conduction loss

4. CONCLUSIONS

The laser characteristics of waveguide sample manufactured by Dr. Ikesue of world laboratory Co., Ltd. were evaluated. Maximum output 120W was obtained from approximately 264 W of absorbed powers. Over 50% of slope efficiency was achieved (target of in this grant) without cracking the sample. However, in the region with 264W or more absorbed power, saturation of the output power occurred. The saturation of this output is thought to be caused by a thermal cooling factor. To obtain higher output power, introducing the high-power sample cooling system is indispensable. The oscillation experiment of higher output is going to be performed in other grant “Basic Research for AOARD 114005 "Evaluation and understanding of the laser oscillation property in waveguides"”.