



**AFRL-RZ-WP-TP-2012-0092**

**PULSED LASER DEPOSITION OF YBCO WITH YTTRIUM  
OXIDE BUFFER LAYERS (POSTPRINT)**

**Paul N. Barnes, Timothy J. Haugan, Nick A. Yust, Juliana M. Evans, and Justin C. Tolliver**

**Mechanical Energy Conversion Branch  
Energy/Power/Thermal Division**

**Rama M. Nekkanti and Lyle B. Brunke  
UES, Inc.**

**Iman Maartense and John P. Murphy  
University of Dayton Research Institute**

**Srinivas Sathiraju  
NRC Fellow**

**Kenneth R. Marken, Jr.  
Oxford Superconducting Technology**

**FEBRUARY 2012**

**Approved for public release; distribution unlimited.**

*See additional restrictions described on inside pages*

**STINFO COPY**

**© 2004 The American Ceramic Society**

**AIR FORCE RESEARCH LABORATORY  
PROPULSION DIRECTORATE  
WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7251  
AIR FORCE MATERIEL COMMAND  
UNITED STATES AIR FORCE**

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. **PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**

<b>1. REPORT DATE (DD-MM-YY)</b> February 2012	<b>2. REPORT TYPE</b> Conference Paper Postprint	<b>3. DATES COVERED (From - To)</b> 01 January 2002 – 01 January 2004
---	---	--

<b>4. TITLE AND SUBTITLE</b> PULSED LASER DEPOSITION OF YBCO WITH YTTRIUM OXIDE BUFFER LAYERS (POSTPRINT)	<b>5a. CONTRACT NUMBER</b> In-house
	<b>5b. GRANT NUMBER</b>
	<b>5c. PROGRAM ELEMENT NUMBER</b> 62203F

<b>6. AUTHOR(S)</b> Paul N. Barnes, Timothy J. Haugan, Nick A. Yust, Juliana M. Evans, and Justin C. Tolliver (AFRL/RZPG) Rama M. Nekkanti and Lyle B. Brunke (UES, Inc.) Iman Maartense and John P. Murphy (University of Dayton Research Institute) Srinivas Sathiraju (NRC Fellow) Kenneth R. Marken, Jr. (Oxford Superconducting Technology)	<b>5d. PROJECT NUMBER</b> 3145
	<b>5e. TASK NUMBER</b> 32
	<b>5f. WORK UNIT NUMBER</b> 314532Z9

<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b> Mechanical Energy Conversion Branch (AFRL/RZPG) Energy/Power/Thermal Division Air Force Research Laboratory Propulsion Directorate Wright-Patterson Air Force Base, OH 45433-7251 Air Force Materiel Command, United States Air Force UES, Inc.	<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b> AFRL-RZ-WP-TP-2012-0092
University of Dayton Research Institute 300 College Park Dayton, OH 45469 ----- NRC ----- Oxford Superconducting Technology 600 Milik Street Carteret, NJ 07008	

<b>9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b> Air Force Research Laboratory Propulsion Directorate Wright-Patterson Air Force Base, OH 45433-7251 Air Force Materiel Command United States Air Force	<b>10. SPONSORING/MONITORING AGENCY ACRONYM(S)</b> AFRL/RZPG
	<b>11. SPONSORING/MONITORING AGENCY REPORT NUMBER(S)</b> AFRL-RZ-WP-TP-2012-0092

**12. DISTRIBUTION/AVAILABILITY STATEMENT**  
Approved for public release; distribution unlimited.

**13. SUPPLEMENTARY NOTES**  
Conference paper published in the proceedings of the *Fabrication of Long-Length and Bulk High-Temperature Superconductors*. The conference was the 105th annual meeting of The American Ceramic Society, held April 27-30, 2003, in Nashville, TN. © 2004 The American Ceramic Society. The U.S. Government is joint author of the work and has the right to use, modify, reproduce, release, perform, display, or disclose the work. Work on this effort was completed in 2004.  
PA Case Number: ASC-03-2987; Clearance Date: 06 Dec 2004.

**14. ABSTRACT**  
Textured metallic substrate based HTS coated conductors with the YBCO/CeO<sub>2</sub>/YSZ/CeO<sub>2</sub>/Ni architecture have already been shown to exhibit high current densities. The CeO<sub>2</sub> seed layer can effectively minimize the formation of NiO during the initial deposition on Ni and the CeO<sub>2</sub> cap layer provides good lattice matching to the subsequent YBCO layer. However, there are reports of cracks developing in the CeO<sub>2</sub> seed layer after a thicker growth due to a lattice mismatch with Ni, which can lead to poor performance of the YBCO conductor. The present work explores an alternate approach by using yttrium oxide not only as the seed layer but also as the cap layer in place of CeO<sub>2</sub>. In the literature, yttrium oxide films grown on nickel by electron beam evaporation processes were found to be dense and crack-free with good epitaxy. This is likely the first report of using Y<sub>2</sub>O<sub>3</sub> as a seed as well as a cap layer within the YBCO coated conductor architecture on specimens being fabricated in a single chamber. Pulsed laser deposition was used to perform deposition of all layers. Preliminary experiments resulted in specimens with current densities of more than 1 MA/cm<sup>2</sup> at 77K in self field. Characterization of samples was accomplished using x-ray diffraction, both resistive and ac susceptibility derived T<sub>c</sub>, and J<sub>c</sub> transport measurements.

**15. SUBJECT TERMS**  
metallic substrates, coated conductors, high current densities, lattice, films, electron, evaporation, layer, chamber, laser, specimens

<b>16. SECURITY CLASSIFICATION OF:</b>	<b>17. LIMITATION OF ABSTRACT:</b> SAR	<b>18. NUMBER OF PAGES</b> 16	<b>19a. NAME OF RESPONSIBLE PERSON (Monitor)</b> Timothy J. Haugan
<b>a. REPORT</b> Unclassified	<b>b. ABSTRACT</b> Unclassified	<b>c. THIS PAGE</b> Unclassified	<b>19b. TELEPHONE NUMBER (Include Area Code)</b> N/A

## PULSED LASER DEPOSITION OF YBCO WITH YTTRIUM OXIDE BUFFER LAYERS

Rama M. Nekkanti,\* Paul N. Barnes, Lyle B. Brunke,\* Timothy J. Haugan, Nick A. Yust, Iman Maartense,\*\* John P. Murphy,\*\* Srinivas Sathiraju,<sup>†</sup> Juliana M. Evans, and Justin C. Tolliver  
Air Force Research Laboratory  
AFRL/PRPG, Building 450  
Wright-Patterson AFB, OH 45433  
\*UES, Inc., \*\*UDRI, <sup>†</sup>NRC Fellow

Kenneth R. Marken, Jr.  
Oxford Superconducting Technology  
600 Milik Street  
Carteret, NJ 07008

### ABSTRACT

Textured metallic substrate based HTS coated conductors with the YBCO/CeO<sub>2</sub>/YSZ/CeO<sub>2</sub>/Ni architecture have already been shown to exhibit high current densities. The CeO<sub>2</sub> seed layer can effectively minimize the formation of NiO during the initial deposition on Ni and the CeO<sub>2</sub> cap layer provides good lattice matching to the subsequent YBCO layer. However, there are reports of cracks developing in the CeO<sub>2</sub> seed layer after a thicker growth due to a lattice mismatch with Ni, which can lead to poor performance of the YBCO conductor. The present work explores an alternate approach by using yttrium oxide not only as the seed layer but also as the cap layer in place of CeO<sub>2</sub>. In the literature, yttrium oxide films grown on nickel by electron beam evaporation processes were found to be dense and crack-free with good epitaxy. This is likely the first report of using Y<sub>2</sub>O<sub>3</sub> as a seed as well as a cap layer within the YBCO coated conductor architecture on specimens being fabricated in a single chamber. Pulsed laser deposition was used to perform deposition of all layers. Preliminary experiments resulted in specimens with current densities of more than 1 MA/cm<sup>2</sup> at 77K in self field. Characterization of samples was accomplished using x-ray diffraction, both resistive and ac susceptibility derived T<sub>c</sub>, and J<sub>c</sub> transport measurements.

---

To the extent authorized under the laws of the United States of America, all copyright interests in this publication are the property of The American Ceramic Society. Any duplication, reproduction, or republication of this publication or any part thereof, without the express written consent of The American Ceramic Society or fee paid to the Copyright Clearance Center, is prohibited.

## INTRODUCTION

Coated high temperature superconductors based on textured substrate technology are in the forefront of developmental efforts towards long length manufacturing of coated conductor tapes for practical applications.<sup>1-3</sup> Significant effort is focused on the development of new metallic substrates based on nickel alloys which are strong, non-magnetic, and are well textured.<sup>4-6</sup> At the same time, different combinations of buffer layers are also being developed to transfer the almost perfect cube texture in the metallic substrate to the  $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$  (YBCO) layer epitaxially. Improvement of the in-plane alignment in the YBCO layer through a suitable seed layer on metallic substrates is an important aspect of the YBCO coated conductor development. The main considerations for the buffer layer are the lattice matching, thermal expansion coefficient matching, chemical compatibility, and ease of deposition.

Previously, a lot of developmental work has concentrated on the YBCO/ $\text{CeO}_2$ /YSZ/ $\text{CeO}_2$ /Ni architecture which resulted in current densities exceeding 1 MA/cm<sup>2</sup> on samples.<sup>7</sup> The initial seed layer of  $\text{CeO}_2$  has been very effective in preventing the formation of NiO, which might otherwise affect the epitaxy of subsequently applied layers. YSZ is a good diffusion barrier preventing the diffusion of nickel into the superconductor. A cap layer is deposited on YSZ to suppress the growth of  $\text{BaZrO}_3$  at the interface between YSZ and YBCO.  $\text{CeO}_2$  is a favored cap layer for YSZ due to its minimal mismatch with both YSZ and YBCO. Even so, interaction between the  $\text{CeO}_2$  and YBCO layer may sometimes occur resulting in the formation of  $\text{BaCeO}_3$  which can lead to a lower current density in the YBCO.<sup>8</sup> Also, the  $\text{CeO}_2$  seed layer cracks after thicker growth due to the lattice mismatch with nickel.

Yttrium oxide ( $\text{Y}_2\text{O}_3$ ) has a better lattice match with nickel and can reduce cracking problems. As such, yttrium oxide has successfully demonstrated replacement for the  $\text{CeO}_2$  as the seed layer, alleviating the potential cracking problems even though  $\text{CeO}_2$  is still preferred for the cap layer.<sup>3</sup> In the literature, there are successful reports of deposition of thick biaxially textured yttrium oxide layers on textured nickel by electron beam evaporation.<sup>9</sup> Ichinose et al. have described the process-related crystalline alignment and microstructure of  $\text{Y}_2\text{O}_3$  buffer layers deposited under various deposition conditions by e-beam evaporation.<sup>10</sup> Paranthaman et al have deposited other buffer layers by sputtering on top of the yttrium oxide followed by pulsed laser deposition of the YBCO layer which resulted in high current densities ( $J_c \sim 1.8 \times 10^6$  A/cm<sup>2</sup>).<sup>11</sup> The present work deals with yttrium oxide replacing  $\text{CeO}_2$  as the seed as well as the cap layer. All layers, including YSZ and YBCO, are deposited in-situ in the same chamber by pulsed laser deposition.

## EXPERIMENTAL

Textured nickel substrates were obtained from Oxford Instruments and the processing details have been presented elsewhere.<sup>6</sup> The substrates have an in-plane alignment of 7.2° FWHM and out-of-plane alignment of 8.4°. The various

oxide buffer layers and YBCO were deposited using pulsed laser deposition system in a Neocera chamber with a Lambda Physik (Model LPX 305i) excimer laser operating at the KrF wavelength of 248 nm. Specimens were fabricated to different stages in the YBCO/CeO<sub>2</sub>/YSZ/CeO<sub>2</sub>/Ni and YBCO/Y<sub>2</sub>O<sub>3</sub>/YSZ/Y<sub>2</sub>O<sub>3</sub>/Ni architecture to study the texture, smoothness and microstructure of the deposited layers. The background pressure in the chamber was brought down to < 10<sup>-6</sup> torr pressure after mounting the specimens on the 2" diameter substrate heater. Specimens were then heated from room temperature to 750 °C in 180 mtorr atmosphere of Ar+4% H<sub>2</sub> (forming gas) gas mixture to prevent oxidation of the nickel substrate.

The layers were applied in-situ in the following manner. After a soaking period of 10 min, the Y<sub>2</sub>O<sub>3</sub> (or CeO<sub>2</sub>) seed layer was deposited at a laser energy of 625 mJ in the Ar+H<sub>2</sub> gas mixture for 3 min at a 4 Hz laser repetition rate. The laser spot size on target was 4.6 mm<sup>2</sup>. The gas fill in the chamber was then evacuated and the chamber was pumped down to a pressure of 10<sup>-6</sup> torr; the deposition of Y<sub>2</sub>O<sub>3</sub> (or CeO<sub>2</sub>) was continued for an additional 1.5 min. Oxygen gas was then introduced in to the chamber and after stabilizing the pressure at 10<sup>-4</sup> torr, the Y<sub>2</sub>O<sub>3</sub> (or CeO<sub>2</sub>) layer was further deposited for 2 min. The temperature was then increased from 750 °C to 780 °C, and the YSZ buffer layer was deposited for 20 min in the oxygen atmosphere at a laser energy of 650 mJ using a 10 Hz frequency. A cap layer of Y<sub>2</sub>O<sub>3</sub> was then deposited at a laser energy of 625 mJ and a 4 Hz repetition rate for 2 min. The oxygen pressure was subsequently increased to 600 mtorr and the superconducting YBCO layer was then deposited on the buffer layers.

The as deposited films were analyzed by detailed x-ray diffraction studies. Two theta scans were accomplished by using a Rigaku x-ray diffractometer. A Philips MRD with four circle diffractometry was used to study the crystalline alignment of the substrate, buffer layers, and the superconductor by means of omega, phi and psi scans. The microstructure of the various films was evaluated under scanning electron microscopy (SEM) to study the surface roughness and morphology of the film structure. Atomic force microscopy (AFM) was used to characterize the roughness of the buffer layers. The quality of YBCO was evaluated by x-ray scans as well as by ac susceptibility measurements to determine the critical transition temperatures (T<sub>c</sub>'s). Electrical property characterizations were made using a standard four-probe technique with a 1 μV/cm criterion to determine the critical current (I<sub>c</sub>).

## RESULTS AND DISCUSSION

The I-V plot of the current measured in the specimen RN-68 at liquid nitrogen temperature, representative of several good samples using Y<sub>2</sub>O<sub>3</sub> as the seed and cap layer, indicated the specimen carried a critical current of 18 A which is equivalent to 1.2 MA/cm<sup>2</sup> of critical current density. Specimen RN-36 at 77K, representative of several good samples using CeO<sub>2</sub> as the seed and cap layer, carried an I<sub>c</sub> of 15 A equivalent to a J<sub>c</sub> of 1.0 MA/cm<sup>2</sup>. Figure 1 shows ac

susceptibility data obtained for RN36 but is representative of both architectures indicating high  $T_c$ . The ac susceptibility plots of the YBCO specimen shown in Figure 1 exhibit an onset  $T_c$  of 90.1 K along with lower transition widths and peak shifts of the  $\chi''$  for varying magnetic field indicating strong inter-grain coupling and a potentially higher  $J_c$ .<sup>12</sup>

Thicker ceria seed layers induced cracking although yttria layers did not crack even as thickness increased. Figure 2 provides an image of the surface of the YBCO microstructure by SEM and AFM. The underlying grain boundaries of the Ni substrate are transferred to the final YBCO layer.

The x-ray theta-two theta scans on YBCO/ $Y_2O_3$ /YSZ/ $Y_2O_3$ /Ni and YBCO/ $CeO_2$ /YSZ/ $CeO_2$ /Ni as well as the intermediate buffer layers, showed sharp (00 $l$ ) peaks indicating excellent c-axis texture in buffer layers which was carried over to the superconducting YBCO layer. Phi scans of the different layers on nickel indicate excellent in-plane alignment of the various layers although slightly better for the ceria architecture: YSZ = 8.3°,  $Y_2O_3$  = 8.0°, and YBCO = 10° for the yttria architecture and for the ceria architecture  $CeO_2$  = 6.7°, YSZ = 6.7°, YBCO = 7.1°. The FWHM of the buffer layers and YBCO did not change much from layer to layer indicating good epitaxy. Refer to Figures 3 and 4 for Psi scans of the two specimens. Figures 3 and 4 provide a comparison between the YSZ and YBCO layer of the samples.



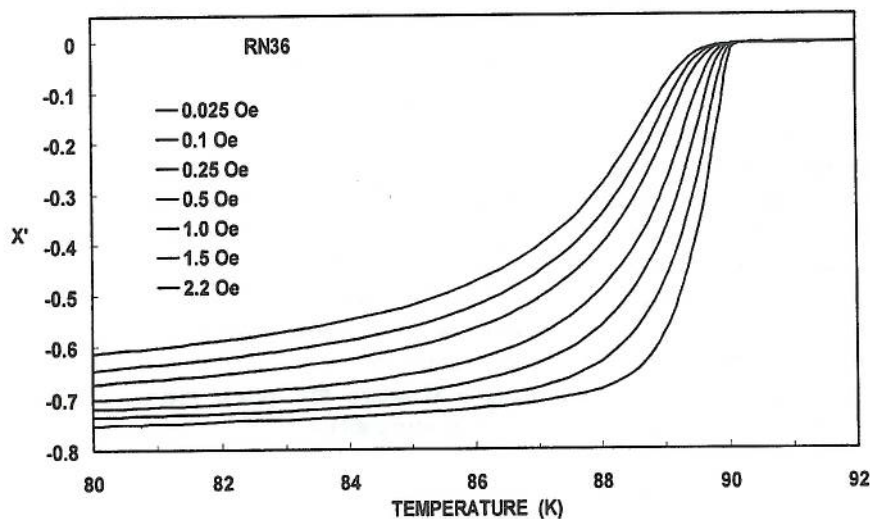


Figure 1. AC susceptibility data for the YBCO/ $CeO_2$ /YSZ/ $CeO_2$ /Ni architecture on a given sample. The different curves result from the different applied fields listed in the legend—the field increases from right to left.

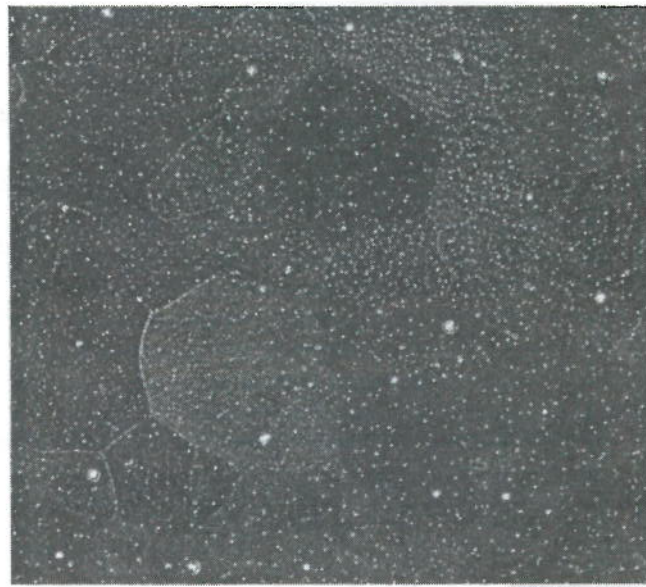

50 $\mu$ m


(A)

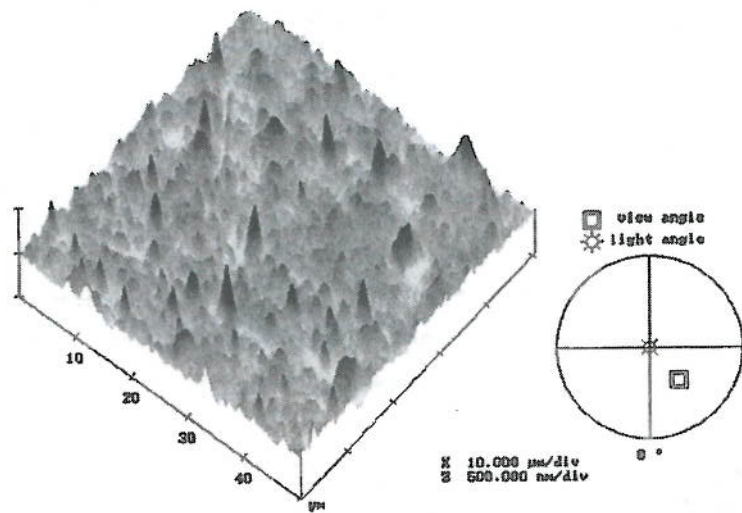

(B)

Figure 2. YBCO layer on specimen RN-68: A) SEM micrograph displaying a large area of the surface microstructure, B) AFM picture showing the surface morphology of a 50  $\mu$ m x 50  $\mu$ m area .

Psi Scan on (111) Peak of YSZ of RN-36

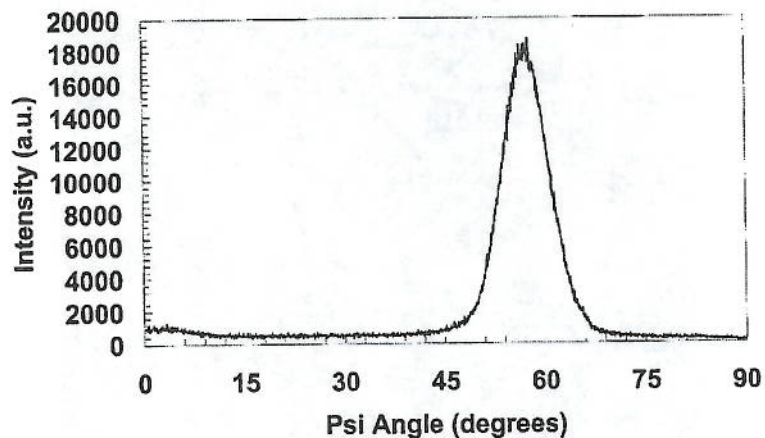

Psi Scan on (111) Peak of YBCO of RN-36

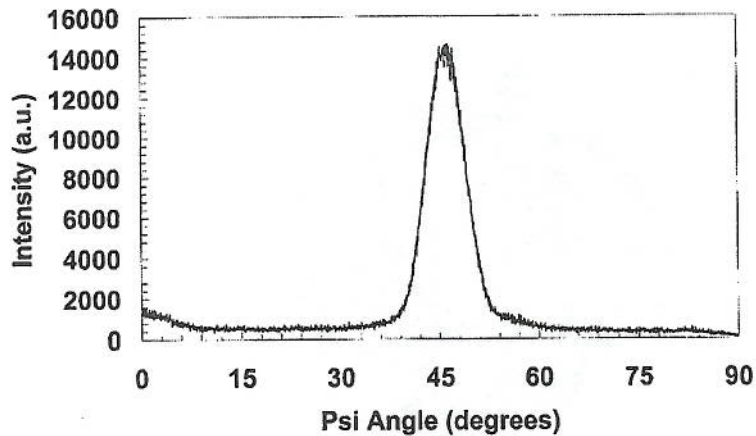


Figure 3. Psi Scan on (111) Peak of YSZ and YBCO layer of specimen RN-36 for the YBCO/CeO<sub>2</sub>/YSZ/CeO<sub>2</sub>/Ni architecture.

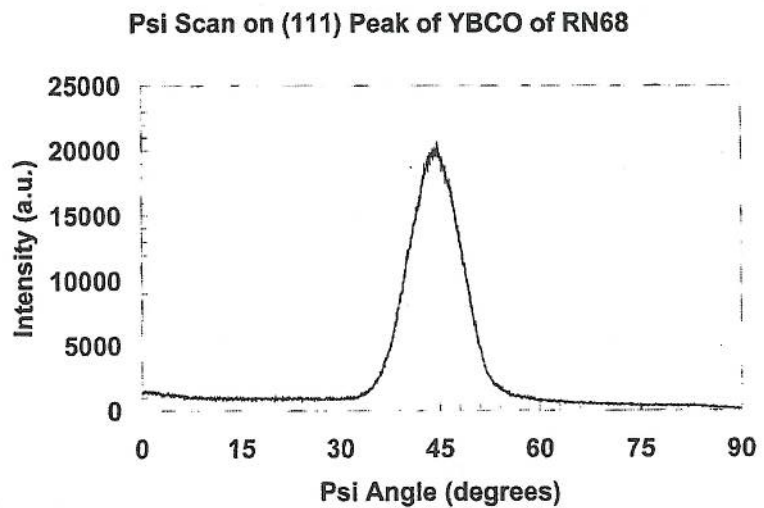
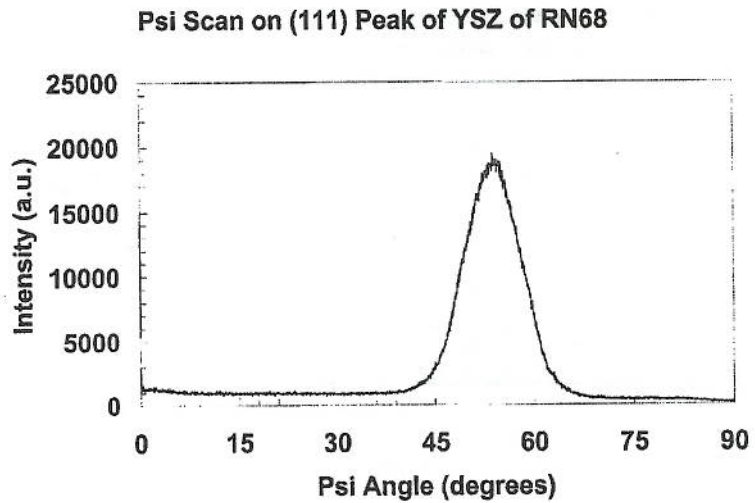


Figure 4. Psi Scan on (111) Peak of YSZ and YBCO layer of specimen RN-68 for the YBCO/Y<sub>2</sub>O<sub>3</sub>/YSZ/Y<sub>2</sub>O<sub>3</sub>/Ni architecture.

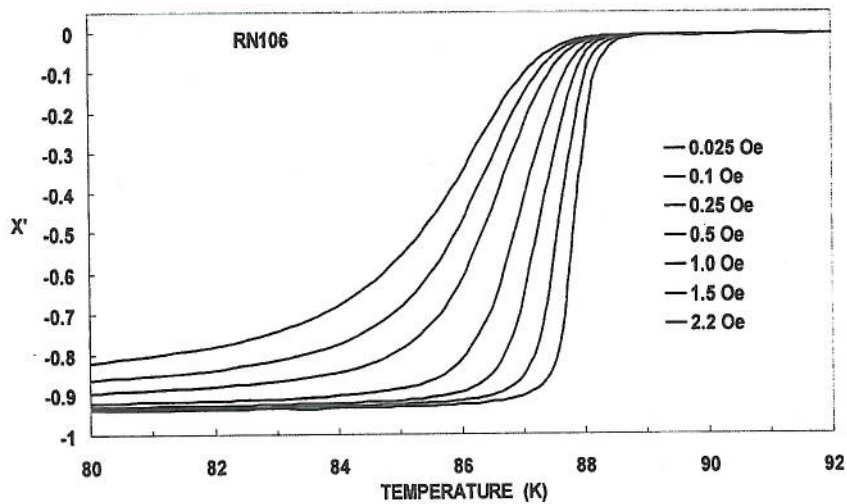


Figure 5. AC susceptibility data for the YBCO/Y<sub>2</sub>O<sub>3</sub>/Ni architecture for a given sample. The different curves result from the different applied fields listed in the legend—the field increases from right to left.

Additionally, a single buffer layer of Y<sub>2</sub>O<sub>3</sub> applied to the Ni substrate was also experimented with. The ac susceptibility plots of the YBCO/Y<sub>2</sub>O<sub>3</sub>/Ni specimen showed a reasonable T<sub>c</sub> (89 K onset) along with slightly broader transition widths and peak shifts of the χ'' for varying magnetic fields compared to those of the traditional YBCO coated conductor architecture. More work needs to be done to optimize the performance using a single Y<sub>2</sub>O<sub>3</sub> buffer layer.

## CONCLUSION

Yttrium oxide was successfully incorporated as both a seed and a cap layer in fabricating the YBCO coated conductor specimens on a textured nickel substrate in a single chamber using pulsed laser deposition. Good epitaxy was observed in all the deposited layers of the YBCO/Y<sub>2</sub>O<sub>3</sub>/YSZ/Y<sub>2</sub>O<sub>3</sub>/Ni architecture leading to a high T<sub>c</sub> (~91 K) and self-field J<sub>c</sub>'s of more than 1 MA/cm<sup>2</sup> on multiple samples. The microstructure of the yttrium oxide and the superconducting YBCO layers were dense, crack-free, and continuous with uniform coverage across the sample.

## REFERENCES

<sup>1</sup>A.C. King, S.S. Shoup, M.K. White, S.L. Krebs, D.M. Mattox, T. Polley, N. Darnell, K.R. Marken, "The progress made using the combustion chemical vapor deposition (CCVD) technique to fabricate YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> coated

conductors,” *IEEE Trans. on Appl. Superconductivity*, **13** [2], pp. 2643 – 2645 (2003).

<sup>2</sup>R.A. Hawsey and A.W. Murphy, *ORNL Superconducting Technology Program for Electric Power Systems, Annual Report for FY 2002*, ORNL/HTSPC-14 (2003).

<sup>3</sup>D.T. Verebelyi, U. Schoop, C. Thieme, X. Li, W. Zhang, T. Kodenkandath, A.P. Malozemoff, N. Nguyen, E. Siegal, D. Buczek, J. Lynch, J. Scudiere, M. Rupich, A. Goyal, E.D. Specht, P. Martin, and M. Paranthaman, “Uniform performance of continuously processed MOD-YBCO-coated conductors using a textured Ni–W substrate,” *Superconductivity Science & Technology*, **16** pp. L19-L22 (2003).

<sup>4</sup>R. Nekkanti, V. Seetharaman, L. Brunke, I Maartense, D. Dempsey, G. Kozlowski, D. Tomich, R. Biggers, T. Peterson, and P. Barnes, “Development of Nickel Alloy Substrates for YBCO Coated Conductor Applications,” *IEEE Trans. on Appl. Superconductivity*, **11**, pp. 3321-3324 (2001).

<sup>5</sup>M. Paranthaman, F. A. List, S. Sathyamurthy, T. Aytug, S. Cook, A. Goyal, and D. M. Kroeger, “Strengthened Ni-W Substrates Produced in 35-m Lengths with Smooth Surfaces and Good Texture,” pp.1-11 to 1-12 in *ORNL Superconducting Technology Program for Electric Power Systems, Annual Report for FY 2002*, Edited by W.S. Koncinski, ORNL Technical Report HTSPC-14, 2003.

<sup>6</sup>K. Marken, B. Czabaj, S. Hong, S. Shoup, M. White, S. Krebs, N. Darnell, T. Polley, D. Mattox, D. Bryson, F. Fortunato, M. Carlin, C. Koehly, and A. Hunt, “Coated Conductor R&D using RABiTS and Combustion Chemical Vapor Deposition,” Dept. of Energy Superconductivity for Electric Systems Annual Peer Review, Washington, DC, July 24, 2003.

<sup>7</sup>C.Y. Yang, S.E. Babcock, A. Goyal, M. Paranthaman, F.A. List, D.P.Norton, D.M. Kroger, A. Ichinose, “Microstructure of electron-beam-evaporated epitaxial yttria-stabilized zirconia/CeO<sub>2</sub> bilayers on biaxially textured Ni tape,” *Physica C*, **307**, pp. 87-98 (1998).

<sup>8</sup>T.G. Holesinger, S.R. Foltyn, P.N. Arendt, Q. Jia, P.C. Dowden, R.F. DePaula, and J.R. Groves, “A Comparison of Buffer Layer Architectures on Continuously Processed YBCO Coated Conductors Based on the IBAD YSZ Process,” *IEEE Trans. on Appl. Superconductivity*, **11** [1], pp. 3359 – 3364 (2001).

<sup>9</sup>M. Paranthaman, D.F. Lee, A. Goyal, E.D. Specht, P.M. Martin, X. Cui, J.E. Mathis, R. Feenstra, D.K. Christen, and D.M. Kroeger, “Growth of biaxially textured RE<sub>2</sub>O<sub>3</sub> buffer layers on rolled-Ni substrates using reactive evaporation for HTS-coated conductors,” *Supercond. Sci. Technol.*, **12**, pp. 319–325 (1999).

<sup>10</sup>A. Ichinose, C. Yang, D. Larbalestier, S. Babcock, A. Kikuchi, K. Tachikawa, S. Akita, “Growth Conditions and microstructure of Y<sub>2</sub>O<sub>3</sub> buffer layers on Cube Textured Ni”, *Physica C*, **324**, pp.113-122, (1999).

<sup>11</sup>D.F. Lee, M. Paranthaman, J.E. Mathis, A. Goyal, D.M. Kroeger, E.D. Specht, R.K. Williams, F.A. List, P.M. Martin, C. Park, D.P. Norton, D.K.

Christen, "Alternative Buffer Architectures for High Critical Current Density YBCO Superconducting Deposits on Rolling Assisted Biaxially-Textured Substrates," *Jpn. J. Appl. Phys.*, **38**, pp. L178-L180 (1999).

<sup>12</sup>I. Maartense and A. K. Sarkar, "Annealing of pressure-induced structural damage in superconducting Bi-Pb-Sr-Ca-Cu-O ceramic," *J. Mater. Res.*, **8**, 2177 (1993).