



AFRL-RW-EG-TP-2013-008

Comparison of Mechanical Properties of Polymer-Based Multi-Phase Particulate Composites

Jennifer L. Jordan¹

Jonathan E. Spowart²

**¹Air Force Research Laboratory
AFRL/RWME, Eglin AFB, FL 32542**

**²Air Force Research Laboratory
AFRL/RXBC, Wright Patterson AFB, OH 45433**

February 2013

Interim Report

This paper was published in Dynamic Behavior of Materials, Volume 1 (2012): 317-320. One or more of the authors is a U.S. Government employee working within the scope of their position; therefore, the U.S. Government is joint owner of the work and has the right to copy, distribute, and use the work. Any other form of use is subject to copyright restrictions.

This work has been submitted for publication in the interest of the scientific and technical exchange. Publication of this report does not constitute approval or disapproval of the ideas or findings.

**Distribution A: Approved for public release; distribution unlimited.
Approval Confirmation 96 ABW/PA # 96ABW-2012-0059, dated
March 1, 2012**

AIR FORCE RESEARCH LABORATORY, MUNITIONS DIRECTORATE

Air Force Materiel Command ■ United States Air Force ■ Eglin Air Force Base

NOTICE AND SIGNATURE PAGE

Using Government drawings, specifications, or other data included in this document for any purpose other than Government procurement does not in any way obligate the U.S. Government. The fact that the Government formulated or supplied the drawings, specifications, or other data does not license the holder or any other person or corporation; or convey any rights or permission to manufacture, use, or sell any patented invention that may relate to them.

Qualified requestors may obtain copies of this report from the Defense Technical Information Center (DTIC) (<http://www.dtic.mil>).

AFRL-RW-EG-TP-2013-008 HAS BEEN REVIEWED AND IS APPROVED FOR PUBLICATION IN ACCORDANCE WITH ASSIGNED DISTRIBUTION STATEMENT.

FOR THE DIRECTOR:

//SIGNED//

MICHAEL A. HYLAND, CAPT, USAF, PhD
Branch Chief
Energetic Materials Branch

//SIGNED//

JENNIFER L. JORDAN, PhD
Munitions Energetic Materials Core
Technical Competency Lead
Ordnance Division

This report is published in the interest of scientific and technical information exchange, and its publication does not constitute the Government's approval or disapproval of its ideas or findings.

This page intentionally left blank

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE (DD-MM-YYYY) 08 Feb 2013		2. REPORT TYPE Interim		3. DATES COVERED (From - To) October 2008 – June 2012	
4. TITLE AND SUBTITLE High Strain Rate Tensile and Compressive Effects in Glassy Polymers				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER 62102F	
6. AUTHOR(S) Jennifer L. Jordan ¹ , Jonathan E. Spowart ²				5d. PROJECT NUMBER 4347	
				5e. TASK NUMBER 95	
				5f. WORK UNIT NUMBER 05	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) ¹ Air Force Research Laboratory, AFRL/RW, Eglin AFB, FL 32542 ² Air Force Research Laboratory, AFRL/RXBC, Wright-Patterson AFB, OH 45433				8. PERFORMING ORGANIZATION REPORT NUMBER AFRL-RW-EG-TP-2013-008	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Research Laboratory, Munitions Directorate Ordnance Division Energetic Materials Branch (AFRL/RWME) Eglin AFB FL 32542-5910 Munitions Energetic Materials Core Technical Competency Lead: Jennifer L. Jordan				10. SPONSOR/MONITOR'S ACRONYM(S) AFRL-RW-EG	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S) AFRL-RW-EG-TP-2013-008	
12. DISTRIBUTION / AVAILABILITY STATEMENT Distribution A: Approved for public release; distribution unlimited. Approval Confirmation 96 ABW/PA # 96ABW-2012-0059, Dated March 1, 2013					
13. SUPPLEMENTARY NOTES SUBJECT TO EXPORT CONTROL LAWS DISTRIBUTION STATEMENT INDICATING AUTHORIZED ACCESS IS ON THE COVER PAGE AND BLOCK 12 OF THIS FORM. DATA RIGHTS RESTRICTIONS AND AVAILABILITY OF THIS REPORT ARE SHOWN ON THE NOTICE AND SIGNATURE PAGE.					
14. ABSTRACT Multi-constituent particulate composites consist of individual particles of more than one material dispersed throughout and held together by a polymer binder. The mechanical and physical properties of the composite depend on the mechanical and physical properties of the individual components, particularly the binder; their loading density; the shape and size of the particles; the interfacial adhesion; residual stresses; and matrix porosity. Multi-constituent composites with cast-cure epoxy binder have been presented recently. In this study, the microstructure is varied by injection molding PMMA-based composites. The dynamic mechanical properties of PMMA-based and epoxy-based composites are measured using a split Hopkinson pressure bar. The mechanical properties of these composites are compared.					
15. SUBJECT TERMS Particulate composites, high strain rate, PMMA, epoxy					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT	b. ABSTRACT	c. THIS PAGE			Jennifer L. Jordan
UNCLASSIFIED	UNCLASSIFIED	UNCLASSIFIED	SAR	11	19b. TELEPHONE NUMBER (include area code) 850-882-8992

This page intentionally left blank

Comparison of Mechanical Properties of Polymer-Based Multi-Phase Particulate Composites

Dr. Jennifer L. Jordan, AFRL/RWME, Eglin AFB, FL 32542
Dr. Jonathan E Spowart, AFRL/RXBC, Wright-Patterson AFB, OH 45433

Abstract

Multi-constituent particulate composites consist of individual particles of more than one material dispersed throughout and held together by a polymer binder. The mechanical and physical properties of the composite depend on the mechanical and physical properties of the individual components, particularly the binder; their loading density; the shape and size of the particles; the interfacial adhesion; residual stresses; and matrix porosity. Multi-constituent composites with cast-cure epoxy binder have been presented recently. In this study, the microstructure is varied by injection molding PMMA-based composites. The dynamic mechanical properties of PMMA-based and epoxy-based composites are measured using a split Hopkinson pressure bar. The mechanical properties of these composites are compared.

Introduction

Polymer composites comprised of metallic particles distributed throughout a contiguous polymer matrix can often be modified to produce advanced composites that exhibit multifunctional characteristics. For example, epoxy with Ni and Al particles [1,2] to produce high strength materials with exothermic reactive properties, or Teflon® (PTFE) can be reinforced with Al and W particles [3]. The properties of the particulate composites often depend on varying particle size, loading fractions, particle type, and the adhesion between the particulate and the matrix [2-6].

Several studies on epoxy-based composites with similar microstructures have been reported. These studies have shown that particle size [3, 7-9], shape [10], and concentration [11] and properties of the constituents can affect mechanical properties. In Al₂O₃ particle-filled epoxy (Epon 828/Z), increasing the particle concentration and decreasing the particle size is found to increase the stress corresponding to 4% plastic strain [12]. A study of aluminum particle filled epoxy (DGEBA/MTHPA) composites has found that a small amount of filler (~ 5 vol.%) increases the compressive yield stress, but additional amounts of filler decrease the compressive yield stress [13]. However, tests on glass-bead-filled epoxy (DOW DER 331/bisphenol-A) found that increasing the volume fraction increased both the yield stress and fracture toughness of the material [14,15]. In another study on a similar material, decreasing the aluminum particle size from micro to nano resulted in increased epoxy crosslink density and subsequently increased both static and dynamic strength [2].

This paper will present the experimental results comparing aluminum and nickel particles in PMMA prepared by injection molding with the same particles in epoxy prepared in a cast-cure process.

Experimental Approach

The samples for this study were prepared using a factorial design of experiments approach in order to maximize the number of variables tested with the minimum number of test specimens. The variables tested were aluminum particle size (5, 30 or 50 μ m), volume percent of aluminum (20, 30, 40 vol.%), and the volume percent nickel (0, 5, 10 vol.%). Two levels and a centerpoint were chosen for the samples. The binder was a thermoplastic, PMMA. These samples compare directly with the epoxy-based samples discussed in previous papers [1, 16], with the exception that the PMMA based samples added a centerpoint to test for curvature. Table 1 shows the details of the factorial design for the PMMA-based samples; the epoxy-based samples are numbered the same starting with MNML and excluding the centerpoint.

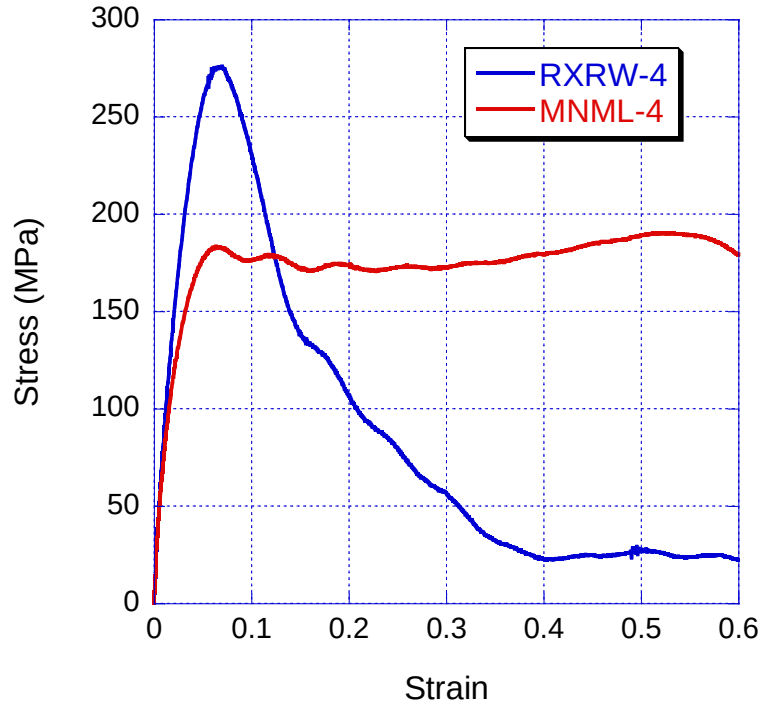
Dynamic compression experiments were conducted using a split Hopkinson pressure bar (SHPB) [17] system at a strain rate of approximately 5000 /s. The bar system is comprised of 1524 mm long, 12.7 mm diameter incident and transmitted bars of 6061-T6 aluminum. The striker is 610 mm long and made of the same material as the other bars. The samples, which were nominally 5 mm diameter by 2.5 mm thick, are positioned between the incident and transmitted bars. The bar faces were lightly lubricated with grease to reduce friction. A complete description of this testing system can be found in Reference 17.

Table 1: Material configurations from a two-level, three factor design of experiments including a centerpoint

Material	Al Particle Size (μm)	Al Volume Fraction (%)	Ni Volume Fraction (%)
RXRW-1	50	40	10
RXRW-2	5	40	10
RXRW-3	50	20	10
RXRW-4	5	20	10
RXRW-5	50	40	0
RXRW-6	5	40	0
RXRW-7	50	20	0
RXRW-8	5	20	0
RXRW-9	30	30	5

Results and Discussion

Both sets of samples, PMMA-based and Epoxy-based, were tested in compression at 5000 /s. Figure 1 shows representative curves from the both materials containing 20 vol.% of 5 μm Al and 10 vol.% Ni. The compressive response of these materials is very different. The epoxy-based composite shows a rise to a peak stress, followed by a small decrease, a region of perfect plasticity and then work hardening, similar to other epoxy-based composites [18]. This is consistent with the deformation of the epoxy binder [17] with the strain softening after the peak decreased potentially due to particle-particle interaction. In contrast, the PMMA-based material shows a rapid rise to a peak stress, followed by a rapid strain softening, and then perfect plasticity at a very low stress. This is consistent with behavior of particulate composites that fail at the peak stress, where the low residual stress is the loading of sample fragments [19].

**Figure 1: Stress-strain response of RXRW-4, PMMA-Al-Ni, and MNML-4, Epoxy-Al-Ni, at a strain rate of 5000 /s.**

The peak stress from both the PMMA-based and epoxy-based samples are plotted versus the total volume fraction of particles in Figure 2. The open symbols are the small aluminum samples and the closed symbols are the large aluminum samples. Additional data from the epoxy-based samples at the same strain rate and a slightly lower strain rate are included for comparison [1]. The trend lines are included to guide the eye rather than as linear fits to the data. There is good agreement between the previously acquired epoxy-based data [1] and that measured in this study. The strengths of the binder materials are included for comparison. For both materials, the small aluminum samples generally have a higher strength than the large aluminum samples. For the epoxy-based, the strength of the composites increases with increasing volume fraction of

particles. For the PMMA-based composites, the strength of the composites decreases with increase in volume fraction of particles. This decrease is believed to be due to the failure of the samples at the peak stress, which could be caused at lower stresses with a higher fraction of particles. These samples were loaded to 50 vol.% total particles. It is interesting that at this point, both the PMMA-based materials and epoxy-based materials seem to be converging to a common peak stress. This stress may be similar to that for a collection of particles as the particle-particle interaction begins to dominate the stress-strain response of the composites, irrespective of the particular polymeric binder used.

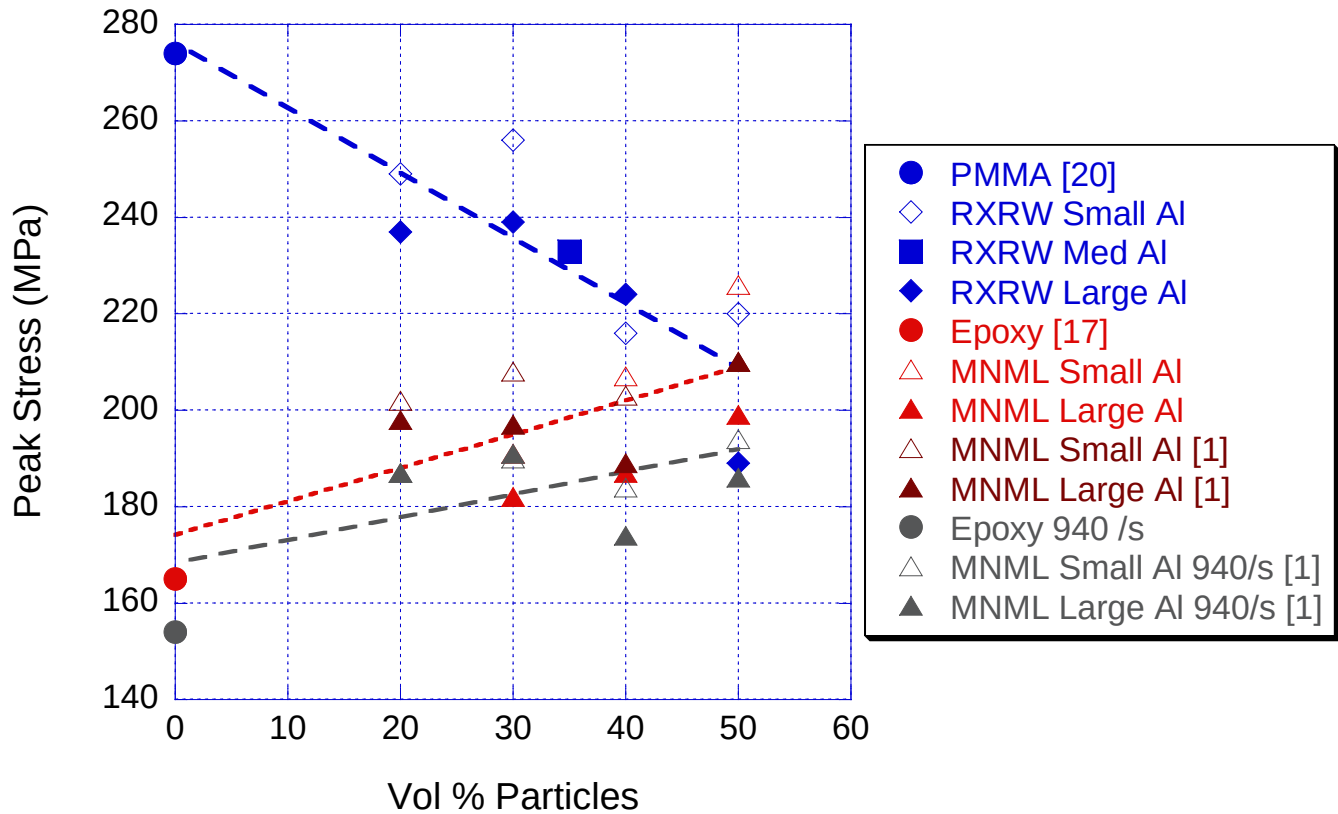


Figure 2: Volume fraction of particles versus peak stress measured using a split Hopkinson pressure bar for RXRW samples (PMMA-Al-Ni) and MNML samples (Epoxy-Al-Ni) where the experimental strain rate is 5000 /s. Open symbols represent samples that contain 5 μ m aluminum and closed symbols represent samples with 50 μ m aluminum.

Summary

Multi-constituent particulate composites consist of individual particles of more than one material dispersed throughout and held together by a polymer binder. The mechanical and physical properties of the composite depend on the mechanical and physical properties of the individual components, particularly the binder; their loading density; the shape and size of the particles; the interfacial adhesion; residual stresses; and matrix porosity. Multi-constituent composites with cast-cure epoxy binder have been presented recently. In this study, the microstructure is varied by injection molding PMMA-based composites. The dynamic mechanical properties of PMMA-based and epoxy-based composites are measured using a split Hopkinson pressure bar. The PMMA-based materials show a rise to peak stress followed by a sharp strain softening, indicating failure of the samples. In contrast, the epoxy-based samples show a nearly perfectly-plastic stress after a rise to peak stress.

Acknowledgements

This research was sponsored by the Air Force Office of Scientific Research (AFOSR), Drs. David Stargel and Joycelyn Harrison, Program Managers. The authors would like to thank Brad White, who created the epoxy-based samples and performed and analyzed the previous characterization of these materials.

Opinions, interpretations, conclusions and recommendations are those of the authors and are not necessarily endorsed by the United States Air Force.

References

1. Jordan, J.L. and J.E. Spowart, "Microstructure Design and Optimization of Highly-Filled Polymer-Based Composites," Air Force Research Laboratory, AFRL-RW-EG-TR-2012-002 (2012).
2. Martin, M., S. Hanagud, and N.N. Thadhani (2007). Mechanical behavior of nickel + aluminum powder-reinforced epoxy composites, *Mat Sci Eng A*, 443: 209-218.
3. Cai, J., Walley, S. M., Hunt, R. J. A., Proud, W. G., Nesterenko, V. F., and Meyers, M. A. (2008). High-Strain, High-Strain-Rate Flow and Failure in PTFE/Al/W Granular Composites, *Mat. Sci. and Eng.*, 472 A: 308-315.
4. Patel, N.R., *Master's Thesis*, Georgia Institute of Technology, Oct. 2004.
5. Fu, S.-Y., Feng, X.-Q., Lauke, B., and Mai, Y.-W (2008). Effects of particle size, particle/matrix interface adhesion and particle loading on mechanical properties of particulate-polymer composites, *Composites: Part B*, 39: 933-961.
6. Clyne, T.W. and Withers, P.J., *An Introduction to Metal Matrix Composites*, 1st Ed., Cambridge University Press, England (1993).
7. Ferranti, L. and N.N. Thadhani (2007). Dynamic mechanical behavior characterization of epoxy-cast Al+Fe₂O₃ thermite mixture composites, *Metal and Matls Trans A*, 38A: 2697-2715.
8. Cai, J., Nesterenko, V.F., Vecchio, K.S., Jiang, F., Herbold, E.B., Benson, D.J., Addiss, J.W., Walley, S.M., and Proud, W.G. (2008). The influence of metallic particle size on the mechanical properties of polytetrafluoroethylene-Al-W powder composites, *Appl Phys Let*, 92: 031903.
9. Herbold, E.B., Nesterenko, V.F., Benson, D.J., Cai, J., Vecchio, K.S., Jiang, F., Addiss, J.W., Walley, S.M., and Proud, W.G. (2008). Particle size effect on strength, failure, and shock behavior in polytetrafluoroethylene-Al-W granular composite materials, *J Appl Phys*, 104: 103903.
10. Ramsteiner, F. and R. Theysohn (1984). On the tensile behavior of filled composites, *Composites*, 15: 121-128.
11. Ferranti, J.L., N.N. Thadhani, and J.W. House (2006). Dynamic mechanical behavior characterization of epoxy-cast Al+Fe₂O₃ mixtures, *AIP Conference Proceedings*, 845: 805-808.
12. Oline, L.W. and R. Johnson (1971). Strain rate effects in particulate-filled epoxy. *ASCE J Eng Mech Div*, 97: 1159-1172.
13. Goyanes, S., Rubiolo, G., Marzocca, A., Salgueiro W., Somoza A., Consolati G., Mondragon I. (2003). Yield and internal stresses in aluminum filled epoxy resin. A compression test and positron annihilation analysis, *Polymer*, 44: 3193-3199.
14. Kawaguchi, T. and R.A. Pearson (2003). The effect of particle-matrix adhesion on the mechanical behavior of glass filled epoxies. Part 1. A study on yield behavior and cohesive strength. *Polymer*, 44: 4229-4238.
15. Kawaguchi, T. and R.A. Pearson (2003). The effect of particle-matrix adhesion on the mechanical behavior of glass filled epoxies. Part 2. A study on fracture toughness, *Polymer*, 44: 4239-4247.
16. Jordan, J.L., J.E. Spowart, B. White, N.N. Thadhani, and D.W. Richards, "Investigation of dynamic mechanical properties of multi-constituent particulate composites based on factorial design of experiments," *Society for Experimental Mechanics Annual Conference on Experimental and Applied Mechanics 2009*, Society for Experimental Mechanics, p. 256-265 (2009).
17. Jordan, J.L., C.R. Siviour, and J.R. Foley, *Mechanical properties of Epon 826/DEA epoxy*. Mechanics of Time Dependant Materials, 2008. **12**(3): p. 249-272.
18. Song, B., W. Chen, S.T. Montgomery, and M.J. Forrestal, "Mechanical Response of an Alumina-Filled Epoxy at Various Strain Rates," *Journal of Composite Materials*, **43** [14], p. 1519-1536 (2010).
19. Rumchik, C.G. and J.L. Jordan, "Effect of Aluminum Particle Size on the High Strain Rate Properties of Pressed Aluminized Explosives," *Shock Compression of Condensed Matter – 2007*, Ed. M. Elert, M.D. Furnish, R. Chau, N. Holmes, and J. Nguyen, p. 795-798 (2007).
20. Jordan, J.L. and C.R. Siviour, unpublished data, 2010.

DISTRIBUTION LIST
AFRL-RW-EG-TP-2013-008

*Defense Technical Info Center
8725 John J. Kingman Rd Ste 0944
Fort Belvoir VA 22060-6218

AFRL/RWME (6)
AFRL/RWOC-1 (STINFO Office)