

Large-Displacement Indentation Testing of Vertically Aligned Carbon Nanotube Arrays

Y.C. Lu · J. Joseph · Q. Zhang · M.R. Maschmann ·
L. Dai · J. Baur

Received: 10 September 2011 / Accepted: 13 March 2012
© Society for Experimental Mechanics 2012

Abstract Mechanical properties and deformation of the vertically aligned carbon nanotube arrays (VA-CNTs) has been examined with large-displacement indentation tests inside a scanning electronic microscope (SEM). The *in-situ* indentation allows for establishment of the load-depth responses and real-time observations of the deformation processes. Under a cylindrical, flat indenter, the VA-CNTs exhibit elastic deformation at small displacement and then plastic deformation at large displacement. The critical indentation pressure (P_m), a measure of collapsing stress of the CNT arrays, is obtained. The magnitude of P_m is approximately equal to the collapsing stress of the carbon nanotube arrays obtained under uniaxial compression.

Keywords Vertically aligned carbon nanotubes · Indentation · Large deformation

Y.C. Lu (✉) · J. Joseph
University of Kentucky,
Lexington, KY 40506, USA
e-mail: chlu@engr.uky.edu

Q. Zhang · M.R. Maschmann · J. Baur
Air Force Research Laboratory,
Materials and Manufacturing Directorate, AFRL/RXBC,
Wright-Patterson AFB, OH 45433, USA

L. Dai
Department of Chemical Engineering, Case Western University,
Cleveland, OH 44106, USA

Q. Zhang
University of Dayton Research Institute, University of Dayton,
Dayton, OH 45469, USA

M.R. Maschmann
Universal Technology Corporation,
Dayton, OH 45432, USA

Introduction

Vertically aligned carbon nanotube arrays (VA-CNTs) have received considerable attention lately due to their unique structures and potential applications. A thorough understanding of the mechanical behaviors of the VA-CNTs is important from the design point of view. The small strain, elastic responses of the CNTs have been studied, mostly through conventional, elastic nanoindentation tests [1–3]. The deformation behaviors of the VA-CNTs at large strain have been investigated recently through compressive testing [4–6]. Under compression, the CNT arrays behave as an open-cell foam-like material, folding themselves in wavelike pattern. The wavelike folding has been observed to always initiate at the bottom of the CNT arrays and then to propagate towards the top. The compressive deformation of the CNTs has been further analyzed through numerical simulations [7]. This paper reports the large-displacement deformation of the VA-CNT arrays by *in-situ*, deep indentation test, with the goals to characterize the plastic properties of the CNT arrays and relevant deformation mechanism.

The large-displacement indentation test has been a proved method for examining the plastic deformation of materials in small volumes [8–10]. Cylindrical, flat tip geometry is typically used for the indenter. Compared to indenters of parabolic and three-face pyramidal shapes, the contact area of a cylindrical flat indenter does not change with displacement, and the extent of the stress field scales with the diameter of the indenter [11]. The present experiments were conducted with an *in-situ* nanoindenter equipped inside the scanning electronic microscope chamber, which revealed both quantitative information (load–displacement) and phenomenological behaviors of the CNT arrays.

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 27 MAR 2012		2. REPORT TYPE		3. DATES COVERED 00-00-2012 to 00-00-2012	
4. TITLE AND SUBTITLE Large-Displacement Indentation Testing of Vertically Aligned Carbon Nanotube Arrays				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Case Western Reserve University, Department of Chemical Engineering, 10900 Euclid Avenue, Cleveland, OH, 44106				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT Mechanical properties and deformation of the vertically aligned carbon nanotube arrays (VA-CNTs) has been examined with large-displacement indentation tests inside a scanning electronic microscope (SEM). The in-situ indentation allows for establishment of the load-depth responses and real-time observations of the deformation processes. Under a cylindrical, flat indenter, the VA-CNTs exhibit elastic deformation at small displacement and then plastic deformation at large displacement. The critical indentation pressure (Pm), a measure of collapsing stress of the CNT arrays, is obtained. The magnitude of Pm is approximately equal to the collapsing stress of the carbon nanotube arrays obtained under uniaxial compression.					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 4	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

Large Displacement Indentation Experiments and Results

The VA-CNTs were synthesized by low pressure chemical vapor deposition (CVD) of acetylene on planar substrates (SiO₂/Si wafers). The catalyst coated substrates were inserted into the quartz tube furnace at 750°C in air for 10 min, followed by pumping the furnace chamber to a pressure less than 1.3 Pa. The growth of the CNT arrays was achieved by flowing a mixture gas of 48% Ar, 28% H₂ and 24% C₂H₂ for 10–20 min. The VA-CNTs were multiwalled (2–3 walls) carbon nanotubes and had a narrow uniform diameter distribution between 10 and 20 nm. The area density of the CNT arrays was estimated as: $\rho = 10^{10} \sim 10^{11}$ tubes/cm². Figure 1 shows the side views of a 215 μm tall CNT arrays.

The large-displacement indentation tests were conducted on as-grown VA-CNTs with a custom designed *in-situ* nanoindenter equipped inside the SEM (FEI Sirion). The

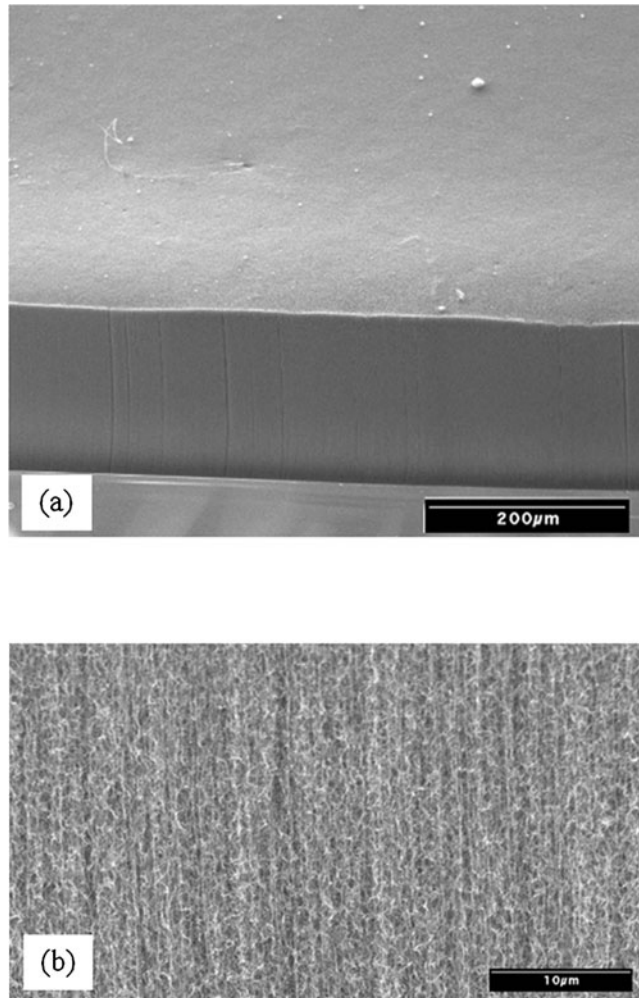


Fig. 1 SEM images showing the morphology of the side surface of the vertically-aligned carbon nanotube arrays ($t=215 \mu\text{m}$)

sizes (heights) of the specimens were chosen carefully to avoid the influence of rigid substrates. The stress field beneath a cylindrical, flat indenter is typically confined within one indenter diameter. Given the size of current indenter (100 μm in diameter), the CNT specimens with heights bigger than 100 μm were used. When a cylindrical indenter of radius a is pressed onto a CNT arrays, the total load (L_{total}) acting on the indenter is the sum of the axial load acting on the indenter end face (L_a) and the frictional load acting on the indenter side wall (L_f). The mean indentation pressure acting on the indenter end is expressed as $P_m = L_a / \pi a^2$. The frictional load (L_f) on the indenter side wall is defined by $L_f = 2\pi a d \tau$, where τ is the frictional shear stress and d the contact depth.

$$L_{total} = L_a + L_f \quad (1)$$

$$\frac{L_{total}}{\pi a^2} = P_m + \frac{2d}{a} \tau \quad (2)$$

The indentation stress- normalized displacement responses of two CNT arrays (215 μm and 1,100 μm in heights) are shown in Fig. 2. Two distinctive regimes can be observed in the indentation stress-displacement curves of the CNT arrays: a short elastic region and a plateau-like plastic region. The plateau region indicates the plastic collapses of carbon nanotubes beneath the indenter face. Such collapse allows the strain increase while the stress stays approximately constant. Since the force required for crushing additional nanotubes is relatively small (because its volume is a small fraction of the material under load), the measurement of the stress associated with the buckling movement are small. Therefore, the total stress at the large strain region has stayed relatively constant. Overall, the stress-displacement response of the CNT arrays is identical to that of an open-cell foam-like material [12, 13].

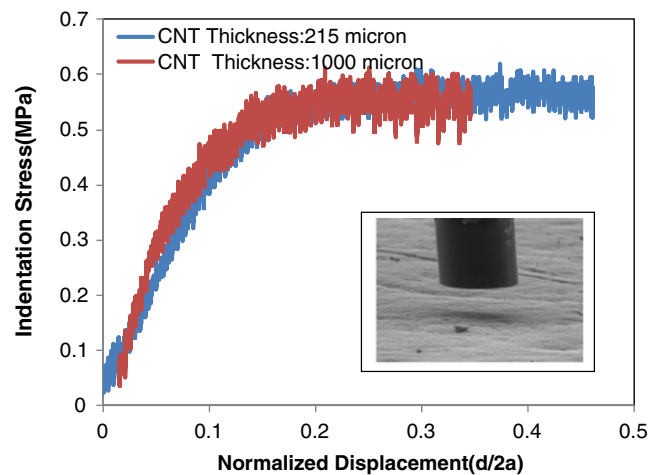


Fig. 2 Indentation stress-displacement curves of vertically aligned carbon nanotube arrays with cylindrical, flat-faced indenter

The normalized stress-displacement curve could then be used to estimate the critical indentation stress (P_m) and the frictional shear stress (τ). For the present CNT arrays, the slopes of stress-displacement at large displacements are almost zero (Fig. 2), indicating that the friction shear stress (τ) on the indenter wall due to the elastic compression from surrounding nanotubes is negligible. This is consistent with the finding reported by Tu et al. [14]. The critical indentation stress, P_m , is determined by extrapolating the large-strain indentation stress-displacement curve back to zero displacement (equation (2)). The magnitude of P_m so obtained for the present CNT arrays is approximately 0.56 MPa.

The same CNT arrays ($t=215 \mu\text{m}$) have been tested under uniaxial compression using the same *in-situ* testing apparatus (Fig. 3). The modulus is calculated from the initial portion of the stress-strain curve, $E=6.8 \text{ MPa}$, consistent with the reported values for typical nanotube arrays [4]. The yield strength is taken as the maximum stress at the peak: $\sigma_y=0.48 \text{ MPa}$. The critical indentation stress (P_m) is proportional to the uniaxial yield stress (σ_y) for a material through a constraint factor: $P_m = C \cdot \sigma_y$ [15]. The constraint effect is due to the confining pressure generated by the surrounding elastically strained material in the indentation stress field. Current results indicate that the critical value of the indentation stress, P_m , is very close to the uniaxial yield stress (σ_y) for the CNT arrays: $P_m/\sigma_y \approx 1.15$. For the foam-like CNT arrays with a plastic Poisson's ratio near zero, the large indentation has resulted in very little lateral spreading of the CNT fibers under the indenter. Thus, the constraint factor becomes unity.

The present *in-situ* nanodenter is equipped inside a SEM chamber, which allows for real-time observation and video recording of the deformation process while the CNT arrays are compressed (Fig. 4). The early stage of penetration is

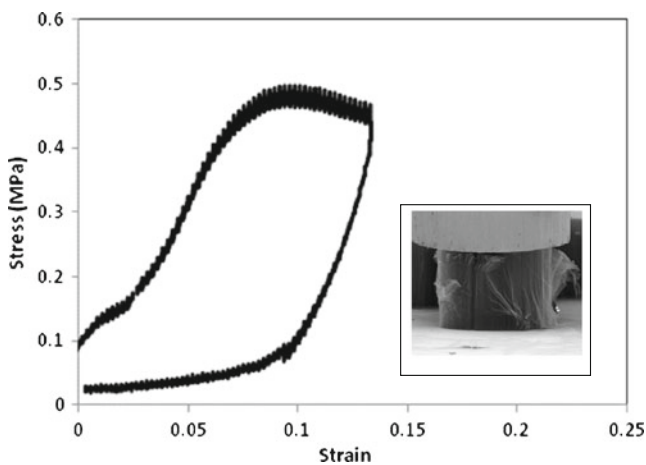


Fig. 3 Compressive stress-strain curve of the vertically aligned carbon nanotube arrays ($t=215 \mu\text{m}$)

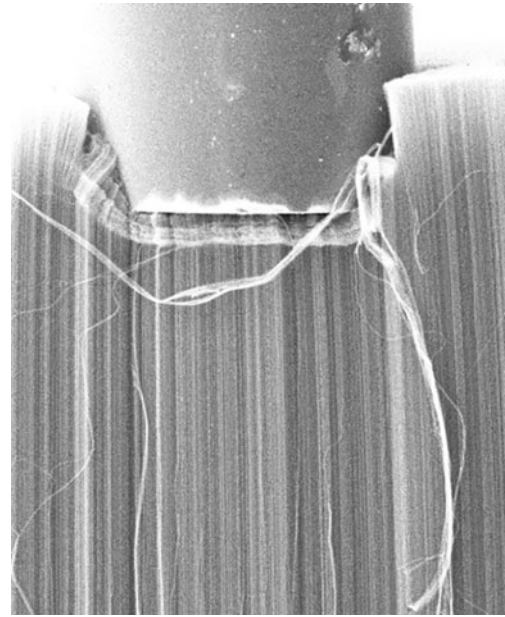


Fig. 4 SEM image showing the development of plastic collapsing of the vertically aligned carbon nanotube arrays under a flat cylindrical indenter ($t=1,100 \mu\text{m}$)

dominated by the elastic deformation. Further penetration of the indenter results in the plastic collapse of the carbon nanotubes immediately beneath the indenter head. Assuming that the CNT arrays are open-cell foam-like materials, the stress and strain fields under a flat indenter have been computed through finite element simulation. Figure 5 shows the resultant equivalent plastic strain (ϵ^{eq}) in the CNT arrays. ϵ^{eq} is defined by $\epsilon^{eq} = \sqrt{\frac{2}{3}(\epsilon_1^2 + \epsilon_2^2 + \epsilon_3^2)}$ and $\epsilon_1, \epsilon_2, \epsilon_3$, are the principal strains. For $\epsilon^{eq} > 0$, the material has yielded. For CNT arrays or foam-like materials, the

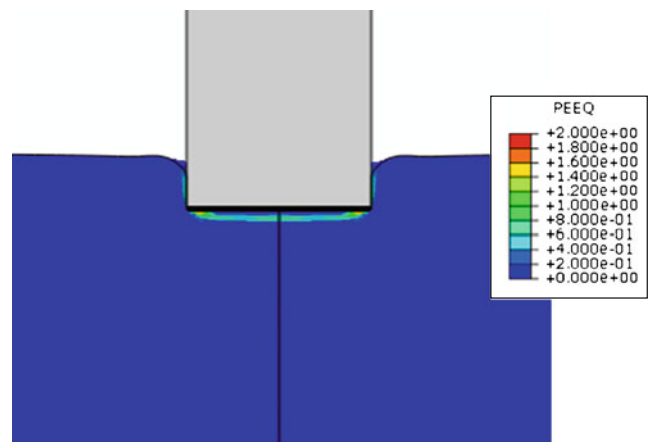


Fig. 5 Finite element calculation of equivalent plastic strain (ϵ^{eq}) in vertically aligned carbon nanotube array material. The material is treated as an open-cell foam-like material

highest strain is seen to occur right beneath the indenter face. The shape of this strain concentration zone is much narrower, as opposed to a larger, hemispherical zone observed in typical dense materials [8–10]. All these suggest that the CNT material would buckle/fold right before the indenter face and then propagates towards to the bottom, which is in contrast with the “bottom-to-top” deformation process occurred under axial compression [4, 5].

Conclusion

Mechanical properties and deformation of the vertically aligned carbon nanotube arrays have been studied through large-displacement indentation tests. Low speed, large-displacement indentation tests were first performed with *in-situ* indentation inside a SEM. The vertically aligned carbon nanotube arrays exhibit a transient elastic deformation at small displacement and then plastic deformation at large displacement. The critical indentation pressure (P_m) can be extrapolated from the indentation stress-displacement curve, which is a measure of the collapsing stress of CNT arrays. The magnitude of P_m at the end of the indenter is approximately equal to the collapsing stress of the same carbon nanotube array under uniaxial compression, indicating that there is negligible interfacial friction between the nanotubes and the indenter sidewall. Under the cylindrical, flat-ended punch, the nanotube cells collapsed plastically immediately beneath the indenter, a region of the highest stress/strain. The plastic deformation remained relatively unchanged in size at large displacement, corresponding to the plateau region on the load-depth curve.

References

1. Mesarovic SDj, McCarter CM, Bahr DF, Radhakrishnan H, Richards RF, Richards CD, McClain D, Jiao J (2007) Mechanical behavior of a carbon nanotube turf. *Scr Mater* 56:157–160
2. McCarter CM, Richards RF, Mesarovic SDj, Richards CD, Bahr DF, McClain D, Jiao J (2006) Mechanical compliance of photolithographically defined vertically aligned carbon nanotube turf. *J Mater Sci* 41:7872–7878
3. Pathak S, Cambaz ZG, Kalidindi SR, Swadener JG, Gogotsi Y (2009) Viscoelasticity and high buckling stress of dense carbon nanotube brushes. *Carbon* 47(8):1969–1976
4. Cao A, Dickrell PL, Sawyer WG, Ghasemi-Nejhad MN, Ajayan PM (2005) Super-compressible foamlike carbon nanotube films. *Science* 310(5752):1307–13
5. Hutchens SB, Hall LJ, Greer JR (2010) *In situ* mechanical testing reveals periodic buckle nucleation and propagation in carbon nanotube bundles. *Adv Funct Mater* 20(14):2338–2346
6. Cao C, Reiner A, Chung C, Chang S, Kao I, Kukta R, Korach CS (2011) Buckling initiation and displacement dependence in compression of vertically aligned carbon nanotube arrays. *Carbon* 49(10):3190–3199
7. Hutchens SB, Needleman A, Greer JR (2011) Analysis of uniaxial compression of vertically aligned carbon nanotubes. *J Mech Phys Solids* 59:2227–2237
8. Wright SC, Huang Y, Fleck NA (1992) Deep penetration of polycarbonate by a cylindrical punch. *Mech Mater* 13:277
9. Lu YC, Shinozaki DM (1998) Deep penetration microindentation testing of high density polyethylene. *Mater Sci Eng A* 249:134–144
10. Lu YC, Kurapati S, Yang F (2008) Finite element analysis of cylindrical indentation for determining plastic properties of materials in small volumes. *J Phys D: Appl Phys* 41:115415
11. Sneddon IN (1946) Boussinesq's problem for a flat-ended cylinder. *Proc Camb Phil Soc* 42:29
12. Wilsea M, Johnson KL, Ashby MF (1975) Indentation of foamed plastics. *Int J Mech Sci* 17:457–460
13. Olurin OB, Fleck NA, Ashby MF (2000) Indentation resistance of an aluminum foam. *Scripta Mater* 43:983–989
14. Tu JP, Zhu LP, Hou K, Guo SY (2003) Synthesis and frictional properties of array film of amorphous carbon nanofibers on anodic aluminum oxide. *Carbon* 41:1257–63
15. Tabor D (1951) *The hardness of metals*. Oxford University Press, Clarendon