

Air Force Materiel Command

One Materiel Command

Environmentally Advantaged Powder Coatings for Aerospace Applications



ESTCP PROJECTS WP-0614 & WP-0801

**Presented at: SERDP/ESTCP Workshop –
Surface Finishing and Repair Issues for
Sustaining New Military Aircraft**

**Presenter: Mr. Christopher Geib
SAIC
26-28 February 2008**

Integrity ~ Service ~ Excellence

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE FEB 2008		2. REPORT TYPE		3. DATES COVERED 00-00-2008 to 00-00-2008	
4. TITLE AND SUBTITLE Environmentally Advantaged Powder Coatings for Aerospace Applications				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Air Force Materiel Command, Wright-Patterson AFB, OH, 45433				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES Surface Finishing and Repair Issues for Sustaining New Military Aircraft Workshop, February 26-28, 2008, Tempe, AZ. Sponsored by SERDP/ESTCP.					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 19	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			



Overview



- **Why Powder Coat**
- **Why Not Powder Coat**
- **Low Temperature Cure Powder Coating (LTCPC) Material (WP-0614)**
- **ESTCP LTCPC Project (WP-0614)**
- **Substrate Test Summary**
- **LTCPC Application Areas**
- **UV-Cure Powder Coat (WP-0801)**
- **Summary**





Why Powder Coat?

- **Eliminates VOCs**
- **Eliminates HAPs**
- **Eliminates Hazardous Waste**
 - Solvent free material – no pot life limitations
- **Reduction of ESOH Concerns**
 - Human Health & Environment
- **Improved Process Efficiency**
 - Quicker cure time
 - Quicker equipment prep and clean-up
 - Improved transfer efficiencies
 - High as 95% versus 50 – 60% for wet paint



Why Not Powder Coat?

- **Previous way of thinking about powder:**
 - High processing temperature
 - High preheat temperatures – as high as 675°F
 - High cure temperatures – typically as high as 428°F
 - Prohibits use on many common alloys – Al, MG
 - No corrosion protection once barrier protection compromised
- **Today's material eliminates these limitations**



LTCPC Material

- **Developed by GE Global Research, Crosslink Powder and DoD Labs with SERDP funding**
- **Program Results - developed a viable low temperature cure coating**
 - Coating cures at 250°F within 30 minutes
 - Corrosion protection
 - Corrosion inhibitor package - barium metaborate
 - Leachable corrosion protection
 - Comparable to conventional solvent borne organic coatings
 - Eliminates need for primer



LTCPC Material

- **Material Advantages**

- SERDP material met all military ground support equipment requirements for durability, toughness, chemical resistance, gloss, and surface quality

- **Coating met all target performance requirements**

- Chemical strippability confirmed
- Cleanability verified using QPL cleaners
- Complete field repair evaluation verified
- Weathering and filiform corrosion tests substantiated

- **The Final Product**

- Acid functional polyester resin and catalyst with triglycidylisocyanurate (TGIC) crosslinker and a barium metaborate type corrosion inhibitor package




ESTCP LTCPC Project (WP-0614)

Taking the LTCPC to the Next Level - Transitioning to the field

This is occurring through an ESTCP funded effort.

Primary Performers/Stakeholders:

- Air Force Corrosion Office (AFCO)
- Air Force Material Command (AFMC)
- Air Logistics Centers - OC-ALC, OO-ALC, WR-ALC
- Concurrent Technologies Corporation (CTC)
- Crosslink Powder Coatings
- Joint Group on Pollution Prevention (JG-PP)
- National Aeronautics and Space Administration (NASA)
- Propulsion Environmental Working Group (PEWG)
- Science Applications International Corporation (SAIC)
- U.S. NAVY

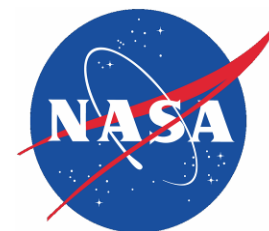



Substrate Test Summary

WP-0614 LTCPC JTP Test Results

Substrate	Appearance	Salt Spray	SO2	Cyclic	Filiform	Adhesion	Impact	Strip	Immersion	Humidity	Gravel	Low T Flex
4130 steel	SAME	SAME	SAME	SAME	--	SAME	--	Note 3	--	--	--	--
2024-T0 Al	SAME	--	--	--	--	--	Note 2	--	--	--	--	Pending
2024-T3 Al (CCC)	SAME	SAME	SAME	--	--	--	--	--	Note 2	Note 2	--	--
2024-T3 Al (No)	SAME	LESS	LESS	--	--	--	--	--	Note 2	Note 2	Note 2	--
6060-T6 Al (CCC)	SAME	SAME	SAME	--	--	--	--	--	--	--	--	--
6060-T6 Al (No)	SAME	LESS	LESS	--	--	--	--	--	--	--	--	--
2024-T3 Clad (CCC)	SAME	SAME	--	BETTR	Note 1	--	--	--	--	--	--	--
2024-T3 Clad (No)	SAME	LESS	--	SAME	Note 1	--	--	--	--	--	--	--
6061-T6 Al (CCC)	SAME	SAME (note 4)	SAME	--	--	SAME	--	Note 3	--	--	--	--
6061-T6 Al (PK)	SAME	SAME (note 4)	LESS	--	--	SAME	--	Note 3	--	--	--	--
AZ31B Mg (Dow)	SAME	SAME	--	--	--	SAME	--	Note 3	--	--	--	--

Legend: LESS=Less than control SAME=Same as control BETTR=Better than control

Note 1: Marginal - Some filiments were up to 0.28 inch.

Note 2: Met requirements in the JTP.

Note 3: Non methylene chloride stripper effective.

Note 4: Exceeded 3300 hrs in salt spray



LTCPC Application Areas



Propulsion systems






LTCPC Application Areas



Non outer mold line components

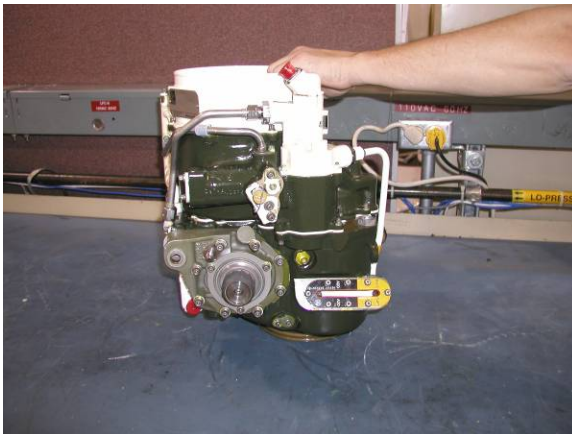



LTCPC Application Areas



Aerospace Ground Equipment (AGE)





UV-Curable Powder Coatings (WP-0801)



- **Objectives:**
 - Demonstrate a VOC/HAP-free, Ultraviolet cure powder coating on DoD depot production hardware to replace solvent-borne organic coatings
 - Demonstrate state-of-the-art robotic curing
 - Verify environmental and economic advantages relative to current solvent-borne technology
 - Validate that UV-cure powder is better in terms of cost, schedule, and performance



UV-Curable Powder Coatings

Technology Description:

- UV-cure powder is an acrylated polyester and polyurethane blend, containing corrosion inhibitor, pigments, photoinitiators, and other constituents
- Powder melts under Infrared heat - as low as 175°F
- The powder is then cured in 5 – 10 seconds using 600W/in Gallium doped UV lamps.

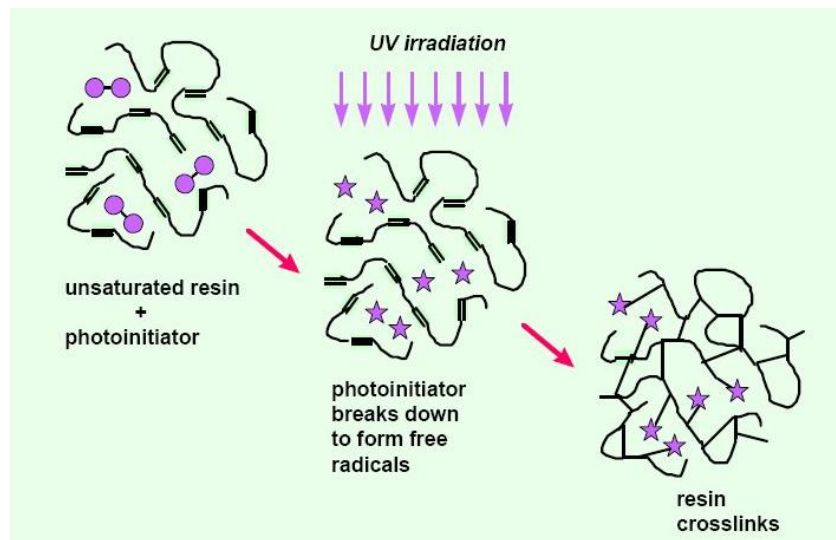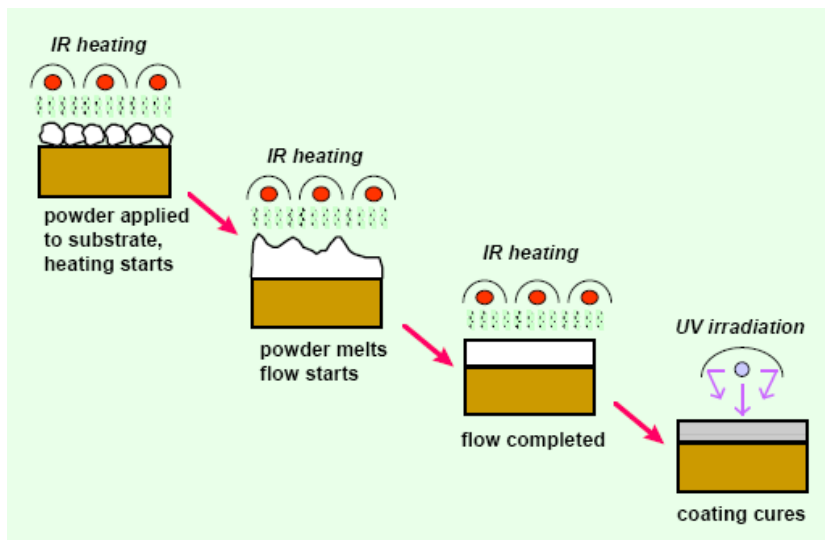



UV-Curable Powder Coatings

Technology Description (cont):


- Reduced thermal exposure enables coating of temperature sensitive components
- Enables large bulky parts to be coated that won't fit into existing curing ovens
- Robotics for melting/curing allows complex shapes such as wheels to be powder coated with improved quality
- UV-cure powder is faster to apply and cure resulting in reduced turnaround times
- UV-cure powder lowers utility cost through reduced cure times (seconds) and elimination of conventional ovens



UV-Curable Powder Coatings

Technology Maturity:

- The first UV-cure powder coating line was opened in 1998 and is still running.
- UV-cure robotics are currently coating and UV-curing automotive wheels and other parts.

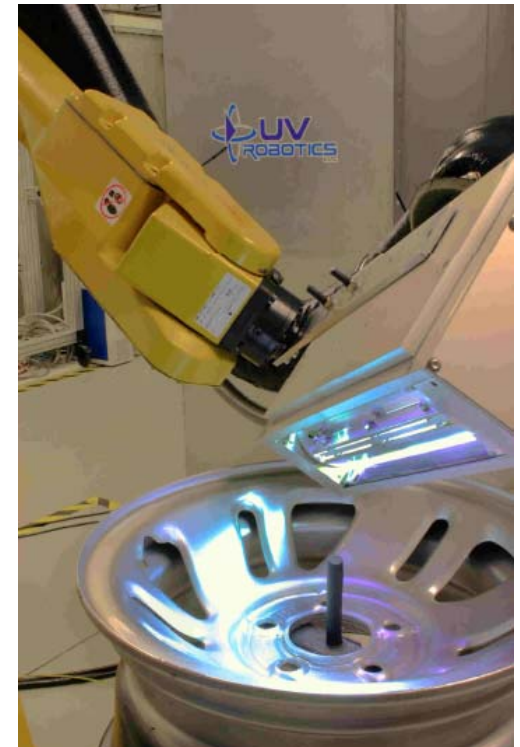



UV-Curable Powder Coatings

Candidate components for UV-cure powder



Internal Components



Aircraft and aircraft
composites



Landing gear



Ground Support Equipment



Aircraft wheels



Summary

- **Traditional high-temp powder coatings were not well suited for aerospace applications**
 - Processing temperatures too high (428°F to 675°F)
 - Provided limited barrier protection (coating only)
- **Powder coating advancements**
 - Low temperature curable powder (as low as 175°F)
 - Ultraviolet curing
 - Corrosion inhibitor packages
- **Powder coatings show promise over wet coatings**
 - Eliminates toxic and hazardous materials from process
 - Reduces labor and utility cost
 - Improves quality, reliability, maintainability, & supportability



Questions?

